

# Energy Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: H. Takeda, M. Sibasaki, K. Murakami, M. Tanaka, K. Makino, N. Tanibata, H. Maeda and M. Nakayama, *Energy Adv.*, 2024, DOI: 10.1039/D4YA00180J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

### Data availability statement

The data that support the findings of this study are available from the corresponding authors upon reasonable request.



## ARTICLE

Effect of synthesis process on the Li-ion conductivity of  $\text{LiTa}_2\text{PO}_8$  solid electrolyte materials for all-solid-state batteriesHayami Takeda,<sup>\*a</sup> Miki Shibasaki,<sup>a</sup> Kento Murakami,<sup>a</sup> Miki Tanaka,<sup>a</sup> Keisuke Makino,<sup>a</sup> Naoto Tanibata,<sup>a</sup> Hirotaka Maeda,<sup>a</sup> and Masanobu Nakayama<sup>\*a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Inorganic solid electrolytes are essential for developing safe and non-flammable all-solid-state batteries, with oxide-based ones having attracted attention owing to their excellent chemical stability. Recently, a new solid electrolyte material  $\text{LiTa}_2\text{PO}_8$  (LTPO) was reported to have a bulk lithium-ion conductivity of  $1.6 \text{ mS cm}^{-1}$  at room temperature, which is one of the highest among oxide solid electrolytes. However, oxide solid electrolytes tend to have a high grain boundary resistivity and must be formed into dense sintered pellets. In this study, different dense LTPO materials were synthesised by adjusting the size of the starting powder particles, and their ionic conductivities were systematically investigated. Counterintuitively, larger raw particles resulted in a lower grain boundary resistivity. This was attributed to the micromorphology of the sintered pellets. The grain boundary resistance varied by up to one order of magnitude under the investigated synthesis conditions, and the optimised total ionic conductivity (including the bulk and grain boundary contributions) of LTPO was  $0.95 \text{ mS cm}^{-1}$  at  $30^\circ\text{C}$ .

## Introduction

The demand for large and safe storage batteries for electric vehicles and smart grids has increased recently, with all-solid-state batteries using non-flammable inorganic solid electrolytes instead of flammable organic electrolytes being more attractive, offering increased safety. Moreover, all-solid batteries can be stacked, are expected to be more compact, and have a higher capacity. Current inorganic solid electrolytes are based on sulfides,<sup>1–3</sup> chlorides,<sup>4–6</sup> and oxides. In particular, oxide-based solid electrolytes exhibit excellent chemical stability and can be assembled under atmospheric conditions. Some well-known examples include perovskite-type (*e.g.*,  $\text{Li}_{3-x}\text{La}_{2/3-x}\text{TiO}_3$ ),<sup>7–9</sup> garnet-type (*e.g.*,  $\text{Li}_7\text{La}_3\text{Zr}_2\text{O}_{12}$ ),<sup>10–13</sup> NASICON-type phosphates (*e.g.*,  $\text{Li}_{1+x}\text{Al}_x\text{Ti}_{2-x}(\text{PO}_4)_3$ ,  $\text{LiZr}_2(\text{PO}_4)_3$ ),<sup>14–21</sup> and LISICON-type materials (*e.g.*,  $\text{Li}_{2+2x}\text{Zn}_{1-x}\text{GeO}_4$ ).<sup>22,23</sup> A common feature of these excellent Li ion-conducting oxides is that their structures contain a framework composed of metal-centred octahedra or tetrahedra that share a vertex.<sup>24</sup>

In 2018, Kim *et al.* conducted a systematic search through the vertex-sharing polyanion  $\text{Li}_x(\text{MO}_{6/2})_m(\text{TO}_{4/2})_n$  phases (where M and T represent octahedral and tetrahedral cation sites, respectively). They developed a novel material, monoclinic  $\text{LiTa}_2\text{PO}_8$  [ $\text{Li}_x(\text{TaO}_{6/2})_2(\text{PO}_{4/2})_1$ , hereafter abbreviated as LTPO], with a bulk conductivity of  $1.6 \text{ mS cm}^{-1}$  and a total conductivity

(including the bulk and grain-boundary contributions) of  $0.25 \text{ mS cm}^{-1}$  at  $25^\circ\text{C}$ . The crystalline system of LTPO is reported to be monoclinic with a  $C2/c$  space group.<sup>24,25</sup> LTPO exhibits excellent water and alkali tolerance.<sup>26</sup> Although the  $\text{P}^{5+}$  and  $\text{Ta}^{5+}$  ions are reduced upon contact with the Li metal anode,<sup>26</sup> stable charge/discharge cycles were possible even when using a Li metal anode by interposing a lithium ion-conductive polyethylene oxide buffer phase between the LTPO and Li metal anode.<sup>26</sup>

Considering the high theoretical lithium-ion conductivity of LTPO ( $35 \text{ mS cm}^{-1}$ ) based on density functional theory calculations,<sup>23</sup> there should be plenty of room for improving its conductivity. To enhance the bulk conductivity, researchers have considered the partial substitution of Ta and P with other elements.<sup>27–29</sup> To reduce the grain boundary resistivity, which is larger than the bulk resistivity, studies have reported the addition of excess Li<sup>30,31</sup> and  $\text{B}_2\text{O}_3$ <sup>32,33</sup> or sintering methods such as spark plasma sintering and hot pressing.<sup>26, 33</sup> However, the highest reported bulk and total conductivities of LTPO at room temperature are  $2.8$  and  $0.7 \text{ mS cm}^{-1}$ , respectively,<sup>33</sup> still more than one order of magnitude lower than the theoretical values. Even when similar preparation conditions are followed, such as equal Li excess and the same firing temperature, the reported lithium-ion conductivities of current LTPO materials differ from author to author.<sup>24,31</sup> This suggests the existence of influencing factors other than raw material composition and heating conditions. Optimising the synthesis process is necessary for improving the conductivity, particularly the grain boundary resistivity. Therefore, in this study, we examined the solid-state reaction of LTPO synthesis to clarify the relationship between

<sup>a</sup> Department of Advanced Ceramics, Nagoya Institute of Technology, Gokiso, Showa, Nagoya, Aichi 466-8555, Japan. E-mail: [takeda.hayami@nitech.ac.jp](mailto:takeda.hayami@nitech.ac.jp)  
Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



the particle size of the raw materials and the ionic conductivity, which influences the reaction rate of the synthetic procedure.

## Experimental Methods

### Synthesis of LTPO pellet

LTPO was synthesised via a solid-state reaction using stoichiometric ratios of Ta<sub>2</sub>O<sub>5</sub> (99.9%; Kojundo Chemical Laboratory, Japan), (NH<sub>4</sub>)<sub>2</sub>HPO<sub>4</sub> (99%; Wako Pure Chemical Industry, Japan), and Li<sub>2</sub>CO<sub>3</sub> (99.9%; Kojundo Chemical Laboratory, Japan). Excess Li<sub>2</sub>CO<sub>3</sub> (10 wt%) was used to compensate for the evaporation of Li<sub>2</sub>O at high temperatures.

All reagents were initially passed through a sieve of mesh size 500 μm. The reagents were further classified using another sieve and mixed according to conditions A–D listed in Table 1. For sample A, unclassified reagents were processed in a planetary ball mill (Pulverisette 7, Fritsch, Germany) with a ZrO<sub>2</sub> pot and balls (5 mm diameter). For samples B–D, Ta<sub>2</sub>O<sub>5</sub> and (NH<sub>4</sub>)<sub>2</sub>HPO<sub>4</sub> were further passed through sieves of mesh sizes 100 and 250 μm. The third reagent (Li<sub>2</sub>CO<sub>3</sub>) was not classified, because its particles were reduced to below 100 μm after a few minutes of mortar grinding. Samples B–D were prepared by mixing the reagents for 20 min using an agate magnetic mortar and a mortar stirrer (VPMS-180BD; AS ONE, Japan). The particle size distribution of the mixed reagent powder was analysed in the dry state using a laser diffraction particle size analyser (Mastersizer 3000, Malvern Panalytical Ltd.UK). The specific surface area of the mixed reagent powder was determined using the Brunauer-Emmett-Teller method via nitrogen gas adsorption analysis (Bellsorp-minill, Microtrac BEL Corp. Japan) at –196 °C. Before analysis, the samples were heated at 80 °C under vacuum for a minimum of 2 hours.

The mixed reagent powders for samples A–D were preheated at 600 °C for 8 h and then at 1000 °C for 8 h (collectively called the 1<sup>st</sup> heating). The 1<sup>st</sup> heating was conducted without pelletisation to avoid any differences in the results caused by the crushing and grinding steps after the formation of the sintered body. The use of powder during the 1<sup>st</sup> heating prevented the introduction of differences in conductivity measurements due to human-derived errors during crushing. Samples agglomerated after the 1<sup>st</sup> heating were processed at 400 rpm for 30 min using a planetary ball mill with a ZrO<sub>2</sub> pot and balls (10 mm diameter). Thereafter, the samples were pelletised and sintered at 1050 °C for 12 h (2<sup>nd</sup> heating) to obtain pellets for conductivity measurements. The sintered pellets were approximately 9 mm in diameter and 1.5 mm in thickness.

### Characterisation

The crystalline phase of the samples was determined via X-ray diffraction (XRD) using a MiniFlex 600 diffractometer (Rigaku, Japan) with CuKα radiation. Rietveld analysis was performed

using RIETAN-FP software.<sup>34</sup> Micromorphology and elemental analyses of the samples were performed via scanning electron microscopy and energy dispersive X-ray spectroscopy (SEM-EDS; JCM-7000 Neoscope, JEOL, Japan). Compositional analysis via X-ray photoelectron spectroscopy (XPS) was performed using an AlKα radiation source (PHI Quantes, ULVAC-PHI, Inc., USA). The bulk density of the sintered pellets (after the 2<sup>nd</sup> heating) was calculated using the weight, diameter, and thickness of the pellets. The diameter and thickness of the sample were measured at three points and the average values were used; the true density of the LTPO sample was assumed to be the theoretical density of LTPO (5.85 g/cm<sup>3</sup>).<sup>35</sup> The relative density was calculated as the ratio of the density of the sample to the theoretical density of LTPO. The ionic conductivities of the pellets were measured after the 2<sup>nd</sup> heating using the AC impedance method. Both sides of the pellet were polished with 2000-grit abrasive paper, and electrodes were prepared on the sides by sputtering gold. The complex impedance was measured with an impedance analyser (VMP-300, BioLogic, France) at –10, 0, 10, and 30 °C, a frequency range of 1–10<sup>6</sup> Hz, and a voltage of 100 mV. The activation energy of lithium transport was calculated using the Arrhenius plot. The electronic conductivity was determined from DC potentiostatic polarisation measurements under a constant voltage of 100 mV for 3600 s, using the pellets after the AC impedance measurements.

## Results

### Characterisation of starting materials after particle size adjustment


The particle size distribution of the adjusted starting materials is illustrated in Fig. S1 (Electronic Supplementary Information, ESI<sup>†</sup>). The median diameters of the prepared samples A, B, C, and D were 7.64, 11.1, 22.6, and 24.1 μm respectively. The nitrogen gas adsorption curves of the adjusted samples and the calculated specific surface area are illustrated in Fig. S2. Sample A exhibited the highest nitrogen adsorption and the highest specific surface area. The nitrogen gas adsorption curves of samples B, C, and D overlapped and no significant difference in their specific surface areas was observed. Figures 1(a–d) shows the SEM images of mixed reagents used to prepare samples A–D (defined in Table 1), respectively. In the ball-milled reagents for sample A, agglomerated particles of about 5 μm were observed, while most of the primary particles were sub-micron or smaller. In the reagents for samples B, C, and D, which were mixed with an agate magnetic mortar, the larger the reagent particle size, the coarser the remaining particles. Fig. S3 shows the distributions of P and Ta elements and the EDS spectra of the starting mixture for sample D. EDS analysis detected Ta and O in the coarse particles, and a small amount of P. Such a finding indicates that Ta<sub>2</sub>O<sub>5</sub> tends to remain as coarse particles without being pulverised.



## ARTICLE


**Table 1.** Sieve sizes and mixing and grinding conditions of samples A–D.

Sample	Sieve sizes for reagents Ta <sub>2</sub> O <sub>5</sub> and (NH <sub>4</sub> ) <sub>2</sub> HPO <sub>4</sub> / μm	Mixing and grinding condition (method / rotation per minute)
A	< 500 (unsieved samples)	ball-mill / 300
B	< 100	magnetic mortar / 140
C	100-250	magnetic mortar / 140
D	250-500	magnetic mortar / 140

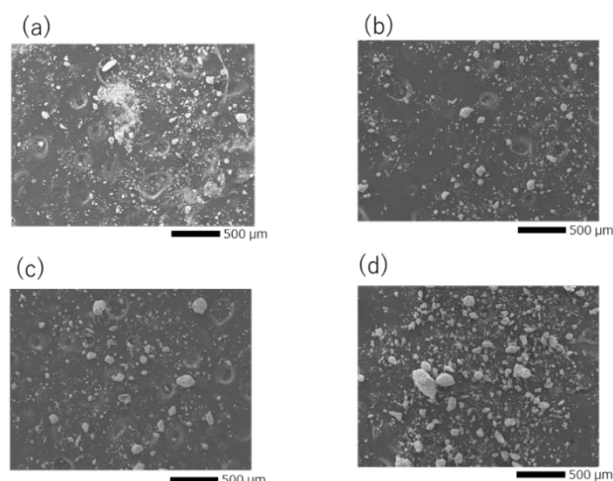**Fig. 1** SEM images of the precursor particles for (a) sample A, (b) sample B, (c) sample C, and (d) sample D.**Temperature dependence of the crystal phase**

To investigate the crystal phases formed at different temperatures, the mixed precursor powders for samples A and D were heated at 750, 850, 950, 1050, and 1100 °C for 30 min. Their XRD patterns are shown in Fig. 2(a) and 2(b), and the identified phases are listed in Table S1. The generated phases depended on the heating temperature. The characteristic patterns of Ta<sub>2</sub>O<sub>5</sub> (inorganic crystal structure database (ICSD: #9112) and TaPO<sub>5</sub> (ICSD: #202041) were identified in both samples A and D heated at 750 and 850 °C. The differences between A and D became more pronounced above 950 °C. The diffraction peaks were broad and low in intensity for sample D, which consisted of the coarsest particles, and the diffraction peaks of Ta<sub>2</sub>O<sub>5</sub> remained unchanged. On the other hand, the characteristic peaks of Ta<sub>2</sub>O<sub>5</sub> disappeared and the peaks indicated by red circles (●) appeared after heating to 950 °C in sample A, which consisted of the smallest primary particles. The peaks indicated by red circles do not correspond to any phase listed in the ICDD database, however, they are in good

agreement with a previously reported phase called β-LiTa<sub>2</sub>PO<sub>8</sub>.<sup>35</sup> Unfortunately, no structural refinement has been performed for this β-LiTa<sub>2</sub>PO<sub>8</sub> phase. Therefore, this phase is referred to as “LTPO-Precursor” in this study. In sample A, the diffraction peaks of LTPO-Crystal (ICSD: #110781) were observed at 1050 °C, whereas sample D did not exhibit any such peaks and only very weak peaks were observed at 1100 °C. The above results confirm that the larger the particle size, the more Ta<sub>2</sub>O<sub>5</sub> remained at higher temperatures, and the higher the temperature at which LTPO-Crystal was synthesised.

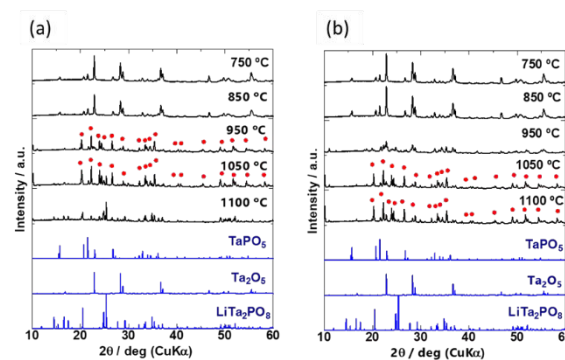
**Fig. 2** XRD patterns of (a) sample A and (b) sample D after heating for 30 min at 750, 850, 950, 1050, and 1100 °C. Bottom: simulated reference patterns based on ICSD for TaPO<sub>5</sub> (#202041), Ta<sub>2</sub>O<sub>5</sub> (#9112), and LiTa<sub>2</sub>PO<sub>8</sub> (#110781). The peaks indicated by red circles are attributed to LTPO-Precursor in this study.

The XRD patterns of the four samples after the 1<sup>st</sup> heating (8 h at 600 °C and then 8 h at 1000 °C) and the 2<sup>nd</sup> heating (12 h at 1050 °C) are shown in Fig. 3(a) and 3(b), respectively. Due to extended exposure to high temperatures during the 2<sup>nd</sup> heating, the XRD patterns in Fig. 3(b) are different from those in Fig. 2. Prolonged heating promoted LTPO formation. As shown in Fig. 3(a), the XRD pattern of sample A after the 1<sup>st</sup> heating matched that of LTPO-Crystals. In contrast, the patterns of samples B, C,





and D after the 1<sup>st</sup> heating only showed very weak characteristic peaks of LTPO-Crystals, matching with those of the LTPO-Precursor (red circles in Fig. 2). After the 1<sup>st</sup> heating, none of the samples showed diffraction peaks of the starting materials such as Ta<sub>2</sub>O<sub>5</sub>. The peak intensity of LTPO-Precursor increased in the order of B < C < D, and a few diffraction peaks of LTPO-Precursor were also observed in sample A after the 1<sup>st</sup> heating. Overall, the results in Fig. 3(a) indicate that LTPO synthesis is more likely to proceed at lower temperatures when the starting mixture consists of smaller particles. Although samples A–D formed different products after the 1<sup>st</sup> heating at 1000 °C, their XRD patterns after the 2<sup>nd</sup> heating at 1050 °C were very similar (Fig. 3(b)), confirming that the main phase of all sintered samples after the 2<sup>nd</sup> heating was LTPO-Crystal. In addition, slight diffraction peaks of LiTa<sub>3</sub>O<sub>8</sub> (ICSD: #493) were observed in all four samples after the 2<sup>nd</sup> heating, which agreed well with previous reports.<sup>24</sup> Rietveld analysis was performed on each sample (Fig. S4) and the content of LiTa<sub>3</sub>O<sub>8</sub> was calculated as A, 2.0 mass%; B, 3.3 mass%; C, 2.1 mass%; D, 2.2 mass%, exhibiting only minor differences in their content. The results of refinement are presented in Table S2-1-5

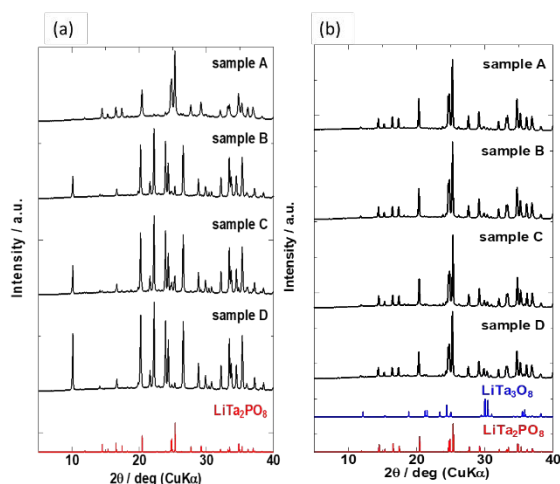


**Fig. 3** XRD patterns of samples (a) after the 1<sup>st</sup> heating and (b) after the 2<sup>nd</sup> heating. Bottom: Simulated reference patterns based on ICSD for LiTa<sub>3</sub>O<sub>8</sub> (#493) and LiTa<sub>2</sub>PO<sub>8</sub> (#110781).


#### Micromorphology, density, and chemical composition

Figures 4 (a)–(d) illustrate SEM images of the sintered pellet surfaces obtained after the 2<sup>nd</sup> heating. All samples were ball-milled under identical conditions after the 1<sup>st</sup> heating, and hence their particle size was approximately the same before the 2<sup>nd</sup> heating. However, the microstructures of the samples after the 2<sup>nd</sup> heating were different. In sample A, where the main phase was LTPO-Crystal after the 1<sup>st</sup> heating, isotropic grains ranging from < 1 to 5 microns were observed. In contrast, samples B, C, and D, in which the formation of LTPO-Crystal was hardly observed after the 1<sup>st</sup> heating, were composed of micrometre-sized grains and uniaxially grown columnar grains, with almost no submicron grains visible. Table S3 shows the

results of the XPS composition analysis for the atomic concentrations of Li and P when the atomic concentration of Ta is converted to 2. Li concentration was smaller with a smaller raw material grain size, however, the observed difference was considered to be an error.

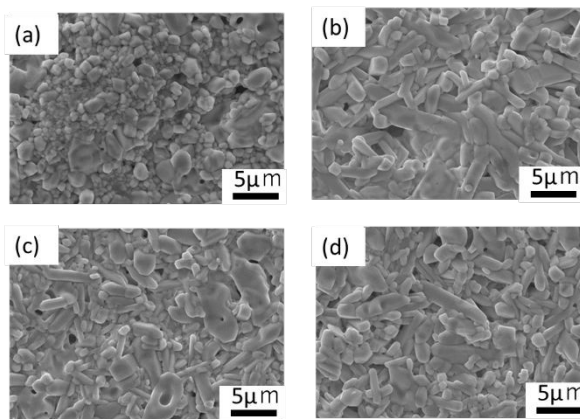

**Fig. 4** SEM images of after the 2<sup>nd</sup> heating for (a) sample A, (b) sample B, (c) sample C, and (d) sample D.

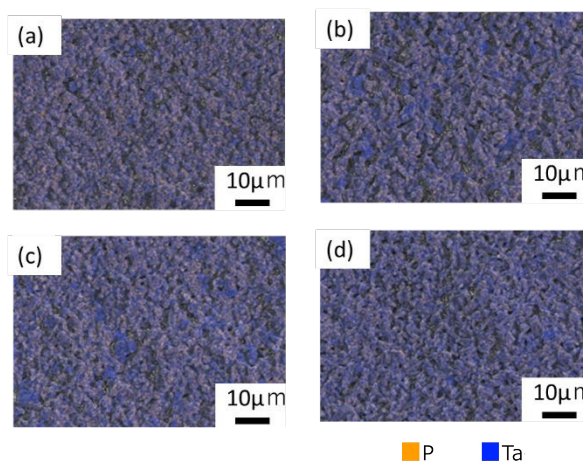


**Fig. 5** P and Ta elemental distribution on the surface after the 2<sup>nd</sup> heating for (a) sample A, (b) sample B, (c) sample C, and (d) sample D.

Figures 5(a)–(d) illustrate the distribution of P and Ta determined by EDS analysis. The distribution of P and Ta was more heterogeneous in samples B and C than in samples A and D. Small quantities of P were detected in areas with high Ta concentration in the SEM-EDS images (Figs. S5 and S6). Based on the XRD profile, it was concluded that the regions rich in Ta and poor in P corresponded to the formation of LiTa<sub>3</sub>O<sub>8</sub>. Table S4 presents the relative densities of the samples after the 2<sup>nd</sup> heating. Sample A, which consisted of smaller grains, exhibited the highest relative density.



### Lithium-ion conductivity

Figs. 6(a) and 6(b) show the AC impedance plots of the samples after the 2<sup>nd</sup> heating at two representative temperatures (30 and -10 °C, respectively). The AC impedance results measured at -10, 0, 10, and 30 °C were fitted with equivalent circuits ( $R_b$ - $CPE_b$ )( $R_{gb}$ - $CPE_{gb}$ )( $CPE_{el}$ ) using Z-view software, where R is the resistance, CPE is the constant phase element, and the subscripts b, gb, and el refer to the bulk, grain boundary, and electrode contributions, respectively. Only one semi-circle is observed in the impedance plot at 30 °C, attributed to the limit of the frequency range of the instrument. The bulk resistance appearing on the high-frequency side is considered to be the resistance represented by the R-CPE parallel circuit from the results of lower temperature measurements. Therefore, fitting with the R-CPE circuit was also employed on the 30 °C data. The obtained capacitances were  $10^{-11}$ – $10^{-10}$  F for the semicircle on the high-frequency side and  $10^{-9}$  F for that on the low-frequency side, corresponding to the bulk and grain boundary resistances, respectively.<sup>13,24,36</sup>

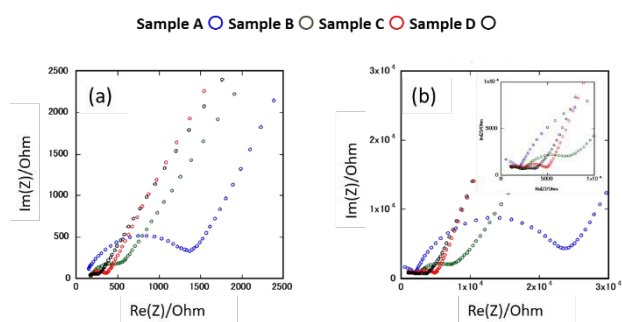


**Fig. 6** AC impedance plots for samples after the 2<sup>nd</sup> heating measured at (a) 30 °C and (b) -10 °C.


Fig. 7 shows the Arrhenius plots of the Li-ion conductivity of samples after the 2<sup>nd</sup> heating. The Li-ion conductivities at each temperature and the activation energies calculated from the Arrhenius plots are listed in Table 2. The bulk and grain boundary resistances at 30 and -10 °C are shown in Fig. 8. The total ionic conductivity increased in the order of  $A < B < C < D$ . The total ionic conductivity of sample A at 30 °C was  $0.19 \text{ mS cm}^{-1}$  and that of sample D was  $0.95 \text{ mS cm}^{-1}$ . Sample A exhibited the lowest total ionic conductivity and the highest density, as shown in Table S4. Fig. 8 also shows that samples A–D exhibit slight differences in their bulk resistance, whereas their grain boundary resistance is ranked as  $D < C < B < A$ . At -10 °C, the grain boundary resistance of sample A is 12 times higher than its bulk resistance, whereas it is about 2.5 times higher in sample B and almost equal in sample D. A similar trend was observed at 30 °C, where the grain boundary resistance of sample D was lower than the corresponding bulk resistance. In all samples, the bulk activation energy was lower than the grain boundary activation energy, and the total activation energy did not differ significantly, as shown in Table 2.

We also investigated the total ionic conductivity of the sample D before and after heating at 200 °C for 1 h in order to remove possible impurities on the surfaces, such as  $\text{LiOH}\cdot x\text{H}_2\text{O}$ . Figure S7 shows the Arrhenius plots of the total ionic conductivity before and after the heating treatment, and no change is indicated. Thus, the effect of impurity phase on the surface is negligible in the present study.

The DC polarisation results for sample D are shown in Fig. S8. Its electronic conductivity is  $1.53 \times 10^{-5} \text{ mS cm}^{-1}$ , which is four orders of magnitude smaller than its ionic conductivity and comparable to the reported value.<sup>24</sup>

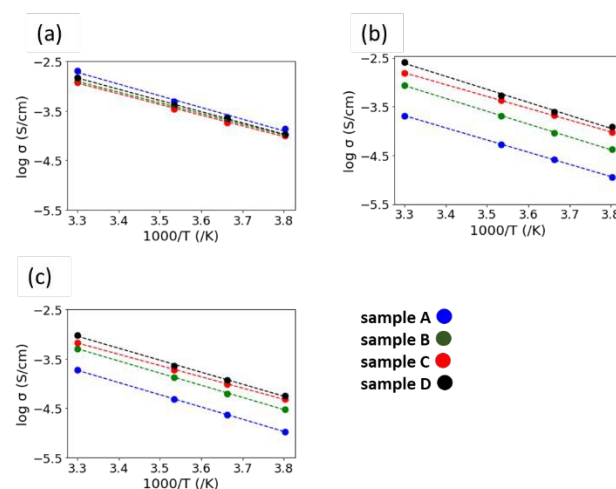

**Fig. 7** Arrhenius plots of the (a) bulk conductivity, (b) grain boundary conductivity, and (c) total ionic conductivity of the samples after the 2<sup>nd</sup> heating.

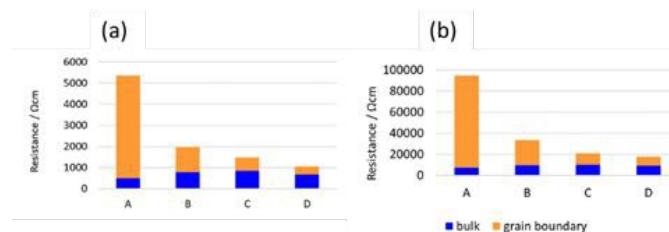

**Fig. 8** Bulk and grain boundary resistances of samples after the 2<sup>nd</sup> heating measured at (a) 30 and (b) -10 °C.



**Table 2** Bulk, grain boundary, and total conductivities at 30, 10, 0, and  $-10$  °C and activation energy for lithium transport of the samples after the 2<sup>nd</sup> heating.

Sample	A	B	C	D	
Conductivity at 30 °C ( mS/cm)	bulk	2.04	1.28	1.20	1.49
	grain boundary	0.21	0.86	1.55	2.59
	total	0.19	0.51	0.68	0.95
Conductivity at 10 °C ( mS/cm)	bulk	0.48	0.38	0.34	0.42
	grain boundary	0.05	0.21	0.42	0.53
	total	0.05	0.13	0.19	0.23
Conductivity at 0 °C ( mS/cm)	bulk	0.24	0.20	0.18	0.22
	grain boundary	0.03	0.09	0.21	0.25
	total	0.02	0.06	0.10	0.12
Conductivity at $-10$ °C ( mS/cm)	bulk	0.14	0.11	0.10	0.11
	grain boundary	0.01	0.04	0.09	0.12
	total	0.01	0.03	0.05	0.06
Activation energy (eV)	bulk	0.47	0.43	0.42	0.45
	grain boundary	0.49	0.52	0.48	0.53
	total	0.49	0.49	0.45	0.48

## Discussion

The synthesis of LTPO using various particle sizes ranging from submicron to hundreds of nanometres confirmed that particle size influenced the LTPO-Crystal formation temperature. The smaller the starting particle size, the lower the temperature at which LTPO-Crystal was formed. Specifically, heating at 1000 °C for 8 h produced LTPO-Crystal in sample A exhibiting the smallest particle size, whereas samples B, C, and D having larger particle sizes mainly generated LTPO-Precursor together with a trace amount of LTPO-Crystal. It was therefore concluded that the Ta<sub>2</sub>O<sub>5</sub> particle size is an important factor for the kinetics of the LTPO-Precursor formation reaction, since the Ta<sub>2</sub>O<sub>5</sub> particles remain as coarse particles in the starting powder mixture without being pulverised, and the coarse Ta<sub>2</sub>O<sub>5</sub> particles remain unreacted until high temperatures due to the low diffusivity of high-valent Ta<sup>5+</sup> ions. The difference in the phases formed during the 1<sup>st</sup> heating had a significant effect on grain growth during the 2<sup>nd</sup> heating. No growth of LTPO-Crystal particles was observed in sample A during the 2<sup>nd</sup> heating, resulting in sintered pellets comprising fine grains. Notably,

sample A exhibited the highest relative density after the 2<sup>nd</sup> heating, indicating the formation of a dense sintered body by a fast-necking process among the particles. Conversely, the growth of LTPO-Crystal particles in samples B–D was clearly visible in a specific direction, and columnar grains were produced during the 2<sup>nd</sup> heating. Such results indicate that the size of Ta<sub>2</sub>O<sub>5</sub> particles in the starting powder mixture affected the formation reaction of LTPO-Precursor and micromorphology of the sintered pellets.

Sample A, which had the smallest particle size in the starting powder mixture, showed the lowest total lithium-ion conductivity, whereas sample D having the largest particle size showed the opposite trend. According to Fig. 8, the difference in the total conductivity among samples A–D was due to the grain boundary conductivity, since there was no large difference in their bulk conductivity. In contrast to the empirical knowledge that using a finer powder as the starting mixture produces homogeneous, dense sintered bodies<sup>37,38</sup> and lowers the grain boundary resistance, our findings indicated the opposite: sample D having the largest particles initially showed the lowest grain boundary resistance after sintering.

Considering the micromorphology and grain boundary resistance, we propose that in the case of sample D, particle





growth during the 2<sup>nd</sup> heating effectively reduced the grain boundary resistance, by shrinking the total grain boundary area. The presence of the LTPO-Precursor phase may control the kinetics of necking and particle growth during the 2<sup>nd</sup> heating. Furthermore, it has been reported that the presence of LiTa<sub>3</sub>O<sub>8</sub> leads to a decrease in conductivity.<sup>33</sup> However, Rietveld analysis demonstrated that sample A, which has the lowest conductivity, contains less LiTa<sub>3</sub>O<sub>8</sub> than the other samples, while samples B, C, and D contain almost the same amount of LiTa<sub>3</sub>O<sub>8</sub>. Therefore, it is unlikely that the difference in conductivity is due to the LiTa<sub>3</sub>O<sub>8</sub> content. It was concluded that the conductivity is influenced by the microstructure and elemental distribution; sample A has the lowest conductivity because it consists of the smallest particles and therefore has the largest grain boundary area (i.e. the highest grain boundary resistance). As illustrated in Fig. 5, the distribution of Ta and P in samples B and C is non-uniform compared to that in sample D, which is thought to have resulted in a higher intergranular resistance than in sample D.

## Conclusion

In this study, we proved that the use of starting materials with a larger particle size can improve the lithium-ion conductivity of synthesised LTPO, primarily due to a reduction in its grain boundary resistance. Furthermore, increasing the raw material particle size inhibited the formation of LTPO crystals and promoted the formation of LTPO-precursor in the 1<sup>st</sup> heating. This finding contradicts the general trend that smaller particles are beneficial for producing homogeneous sintered samples with a low grain boundary resistance. Sample A, in which LTPO-Crystal was produced during the 1<sup>st</sup> heating, formed a sintered structure during the 2<sup>nd</sup> heating with a relatively high relative density but without visible particle growth. Furthermore, it exhibited the highest grain boundary resistance. In contrast, sample D containing coarser particles exhibited significant particle growth without the formation of the LiTa<sub>3</sub>O<sub>8</sub> impurity phase, having the lowest grain boundary resistance after sintering. These findings suggest that the grain boundary resistance could be reduced by promoting particle growth, which lowers the proportion of grain boundaries. Such a conclusion is contrary to the general trend that smaller particles are beneficial for producing homogeneous sintered samples with a low grain boundary resistance. It was also found that the composition remained nearly constant irrespective of the synthesis conditions, however, the inhomogeneous concentration of the constituent elements in the sintered microstructure reduced the ionic conductivity. The conductivity was reduced in the samples that did not exhibit the formation of any intermediate products after the first sintering. This suggests that in the case of compounds such as LTPO, where intermediate products are formed during the synthesis process, the raw material particle size and sintering conditions affect the sintered body microstructure and significantly change the intergranular ionic conductivity properties. In this study, the same heating conditions were applied to the four samples.

This journal is © The Royal Society of Chemistry 20xx. *Name.*, 2013, **00**, 1-3 | 7

Optimising the firing conditions can lead to further improvements in conductivity. [View Article Online](#)  
DOI: 10.1039/D4YA00180J

## Author Contributions

H. T. and M. N. conceived and designed the study. H.T., M. S., K. Mu., M. T., K. Ma., and H. M. performed the experiments and analysed the data. The manuscript was mainly written by H. T. and M. N. with contributions from all authors. All the authors approved the final version of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was partially supported by the Grant-in-Aid for Scientific Research (grant numbers 19H05815, 20H02436, 21K04650, 21K14715, 21K04650, 21H01625, and 22H02179) from the Ministry of Education, Culture, Sports, Science, and Technology (MEXT), Japan; Data Creation and Utilization-Type Material Research and Development Project (grant number, JPMXP1122712807) from MEXT and JST CREST (grant number: JPMJCR21D3). English language editing was done by Editage (www.editage.com).

## References

- 1 N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto and A. Mitsui, *Nat. Mater.* 2011, **109**, 2011, 682–686.
- 2 A. Kuhn, O. Gerbig, C. Zhu, F. Falkenberg, J. Maier and B. V. Lotsch, *Phys. Chem. Chem. Phys.*, 2014, **16**, 14669–14674.
- 3 Y. Kato, S. Hori, T. Saito, K. Suzuki, M. Hirayama, A. Mitsui, M. Yonemura, H. Iba and R. Kanno, *Nat. Energy* 2016, **14**, 1–7.
- 4 X. Li, J. Liang, X. Yang, K. R. Adair, C. Wang, F. Zhao and X. Sun, *Energy Environ. Sci.*, 2020, **13**, 1429–1461.
- 5 N. Tanibata, S. Takimoto, S. Aizu, H. Takeda and M. Nakayama, *J. Mater. Chem. A*, 2022, **10**, 20756–20760.
- 6 N. Tanibata, S. Takimoto, K. Nakano, H. Takeda, M. Nakayama and H. Sumi, *ACS Mater. Lett.*, 2020, **2**, 880–886.
- 7 Y. Inaguma, L. Chen, M. Itoh and T. Nakamura, *Solid State Ionics*, 1994, **70–71**, 196–202.
- 8 O. Bohnke, C. Bohnke and J. L. Fourquet, *Solid State Ionics*, 1996, **91**, 21–31.
- 9 Y. H. Cho, J. Wolfenstine, E. Rangasamy, H. Kim, H. Choe and J. Sakamoto, *J. Mater. Sci.*, 2012, **47**, 5970–5977.
- 10 R. Murugan, V. Thangadurai and W. Weppner, *Angew. Chemie Int. Ed.*, 2007, **46**, 7778–7781.



- 11 R. Iwasaki, K. Ishida, R. Yasuda, K. Nakano, N. Tanibata, H. Takeda, M. Nakayama and N. Watanabe, *Phys. status solidi*, 2022, 2100546.
- 12 Z. Yang, S. Suzuki, N. Tanibata, H. Takeda, M. Nakayama, M. Karasuyama and I. Takeuchi, *J. Phys. Chem. C*, 2021, **125**, 152–160.
- 13 I. N. David, T. Thompson, J. Wolfenstine, J. L. Allen and J. Sakamoto, *J. Am. Ceram. Soc.*, 2015, **98**, 1209–1214.
- 14 H. Xie, Y. Li and J. B. Goodenough, *RSC Adv.*, 2011, **1**, 1728.
- 15 H. Fukuda, S. Kusakawa, K. Nakano, N. Tanibata, H. Takeda, M. Nakayama, M. Karasuyama, I. Takeuchi, T. Natori and Y. Ono, *RSC Adv.*, 2022, **12**, 30696–30703.
- 16 M. Nakayama, K. Nakano, M. Harada, N. Tanibata, H. Takeda, Y. Noda, R. Kobayashi, M. Karasuyama, I. Takeuchi and M. Kotobuki, *Chem. Commun.*, 2022, 58, 9328–9340.
- 17 M. Harada, H. Takeda, S. Suzuki, K. Nakano, N. Tanibata, M. Nakayama, M. Karasuyama and I. Takeuchi, *J. Mater. Chem. A*, 2020, **8**, 15103–15109.
- 18 Y. Li, W. Zhou, X. Chen, X. Lü, Z. Cui, S. Xin, L. Xue, Q. Jia and J. B. Goodenough, *Proc. Natl. Acad. Sci. U. S. A.*, 2016, **113**, 13313–13317.
- 19 H. Aono, E. Sugimoto, Y. Sadaoka, N. Imanaka and G. Adachi, *J. Electrochem. Soc.*, 1989, **136**, 590–591.
- 20 B. Lang, B. Ziebarth and C. Elsässer, *Chem. Mater.*, 2015, **27**, 5040–5048.
- 21 H. Takeda, H. Fukuda, K. Nakano, S. Hashimura, N. Tanibata, M. Nakayama, Y. Ono and T. Natori, , DOI:10.1039/d2ma00731b.
- 22 R. Kanno, T. Hata, Y. Kawamoto and M. Irie, *Solid State Ionics*, 2000, **130**, 97–104.
- 23 L. Zhang, M. Malys, J. Jamroz, F. Krok, W. Wrobel, S. Hull, H. Yan and I. Abrahams, *Inorg. Chem.*, 2023, **62**, 11876–11886.
- 24 J. Kim, J. Kim, M. Avdeev, H. Yun and S. J. Kim, *J. Mater. Chem. A*, 2018, **6**, 22478–22482.
- 25 N. Ishigaki, K. Kataoka, D. Morikawa, M. Terauchi, K. Hayamizu and J. Akimoto, *Solid State Ionics*, 2020, **351**, 115314.
- 26 B. Huang, B. Xu, J. Zhang, Z. Li, Z. Huang, Y. Li and C. A. Wang, *J. Mater. Sci.*, 2021, **56**, 2425–2434.
- 27 J. Lei, Z. Liu, H. Wang, Z. Li, R. Liao, S. Dmytro and Q. Zhang, *Ceram. Int.*, 2023, **49**, 1980–1986.
- 28 Z. L. Jingang Lei and Z. Q. Li Ziwei, Haizhong Wang, Dmytro Sydorov, *J. Energy Storage*, 2023, **72A** 108080.
- 29 S.-Y. Y. Hyeonjin Kim, Sinho Choi, Dong-Hyun Peck, *Ceram. Int.*, 2023, **49**, 8718–8724.
- 30 Q. Zhang, F. Meng, R. Liao, L. Chen, M. Xu, S. Zhong, J. Chen and A. Lu, *Front. Mater.*, 2021, **8**, 670754
- 31 K. Kwatek, W. Ślubowska-Walkusz, E. Kwiatkowska, J. L. Nowiński, A. T. Krawczyńska, I. Sobrados, V. Diez-Gómez and J. Sanz, *J. Eur. Ceram. Soc.*, 2023, **43**, 5548–5556.
- 32 Z. Liu, J. Lei, W. Liu, B. Fang, L. Xie, S. Dmytro and Q. Zhang, *J. Eur. Ceram. Soc.*, 2023, **43**, 4437–4442.
- 33 R. Dai, M. Avdeev, S.-J. Kim, R. P. Rao and S. Adams, *Chem. Mater.*, 2022, **34**, 10571–10583.
- 34 F. Izumi, K. Momma, Three-dimensional visualization in powder diffraction, *Solid State Phenom.*, 2007, **130-15-20-35**  
DOI:10.1007/s11464-007-1891-1
- 35 R. Kim, L. J. Miara, J. H. Kim, J. S. Kim, D. Im and Y. Wang, *Chem. Mater.*, 2021, **33**, 6909–6917.
- 36 J. T. S. Irvine, D. C. Sinclair and A. R. West, *Adv. Mater.*, 1990, **2**, 132–138.
- 37 E. Traversa, P. Nunziante, M. Sakamoto, Y. Sadaoka, *Materials Research Bulletin*, 1998, **33**, 673–681
- 38 M. Hirano, E. Kato, *J. Am. Ceram. Soc.*, 1996, 579–816

