


 Cite this: *RSC Adv.*, 2020, 10, 10510

Synthesis of a hierarchical carbon fiber@cobalt ferrite@manganese dioxide composite and its application as a microwave absorber

 Ailing Feng,^a Tianqi Hou,^b Zirui Jia^{*b} and Guanglei Wu ^{*bc}

In this study, a novel hierarchical carbon fiber@cobalt ferrite@manganese dioxide (CF@CoFe₂O₄@MnO₂) composite was facily prepared *via* a sol–gel method and hydrothermal reaction. The morphology, structure, chemical and element composition, crystal form, elemental binding energy, magnetic behavior and microwave absorbing performance of the composite were carefully investigated. According to its hysteresis loops, the composite exhibits a typical soft magnetic behavior, with a M_s value of 30.2 emu g⁻¹. Besides, the as-synthesized CF@CoFe₂O₄@MnO₂ composite exhibits superior microwave absorption performance mainly due to reasonable electromagnetic matching, and its minimum reflection loss value can reach –34 dB with a sample thickness of just 1.5 mm. The composite can be regarded as an ideal microwave absorber.

 Received 9th December 2019
 Accepted 27th February 2020

DOI: 10.1039/c9ra10327a

rsc.li/rsc-advances

1. Introduction

In recent years, the universal applications of computer technology, electromagnetic medicine, broadcasting, and communication have made microwaves part of human beings' daily lives. Thus, the harm caused by microwaves to humans and their interference with related equipment is receiving increasing attention from all over the world.^{1–6} Simultaneously, in order to achieve microwave protection, research on microwave absorbing materials has also been rapidly growing. According to the dielectric loss and magnetic loss mechanisms of the microwave, an ideal microwave absorber ought to possess both selective dielectric properties and magnetic properties.^{7–10} Therefore, the combination of dielectric materials (such as carbon-based materials, conductive polymers, and transition metal oxides) and magnetic materials (metal iron, cobalt, nickel and their compounds) by chemical reactions has been a classic research method for obtaining superior microwave absorbing composites.^{11–17}

As a typical soft magnetic material, cobalt ferrite has been widely applied in the preparation of efficient microwave absorption composites. Lv *et al.*¹⁸ developed a novel core/shell α -Fe₂O₃@CoFe₂O₄ composite, which showed excellent EM wave absorbing performance, with a minimum

reflection loss value of –41 dB. Besides, RGO/CoFe₂O₄,¹⁹ CNT/CoFe₂O₄ (ref. 20) and PANI/CoFe₂O₄ (ref. 21) also exhibit superior microwave absorption performance due to the fair electromagnetic matching.

In view of its strong dielectric properties, manganese dioxide has become an interesting research material when regarded as a microwave absorber. Among others, MnO₂ possesses many advantages such as strong designability, simple synthesis method, good stability, and low price. Recently, an ideal microwave absorber comprising a hierarchical Fe₃O₄@carbon@manganese dioxide hybrid has been reported by Chen *et al.*²² The hybrid showed an excellent microwave absorption capacity based on the improvement of dielectric properties by MnO₂ with a minimum reflection loss value of –35 dB when the sample thickness is 2.7 mm. Besides, numerous other superior microwave absorbers related to MnO₂ such as PANI/MnO₂/CF,²³ NiFe₂O₄/MnO₂,²⁴ carbonyl iron/MnO₂ (ref. 25) were also reported. Thus, it is significant to develop a microwave absorber by using MnO₂.^{26–28}

In this study, a novel CF@CoFe₂O₄@MnO₂ composite was facily prepared. First, a typical sol–gel reaction was adopted to prepare the CF@CoFe₂O₄ composite. Then, the as-synthesized CF@CoFe₂O₄ composite was further coated with MnO₂ *via* a hydrothermal reaction to obtain the CF@CoFe₂O₄@MnO₂ composite. The morphology, structure, chemical and element composition, crystal form, elemental binding energy, magnetic behavior, and microwave absorbing performances of the composite were carefully investigated. According to its hysteresis loops, the composite exhibited a typical soft magnetic behavior, with a M_s value of 30.2 emu g⁻¹. Besides, the as-synthesized CF@CoFe₂O₄@MnO₂ composite possesses a superior microwave absorption performance mainly due to reasonable electromagnetic matching, and its minimum reflection

^aInstitute of Physics & Optoelectronics Technology, Baoji University of Arts and Sciences, Baoji 721016, P. R. China

^bInstitute of Materials for Energy and Environment, State Key Laboratory of Bio-fibers and Eco-textiles, College of Materials Science and Engineering, Qingdao University, Qingdao 266071, P. R. China. E-mail: jiazirui@mail.mwpu.edu.cn; wuguanglei@mail.xjtu.edu.cn; wuguanglei@qdu.edu.cn; Fax: +86 532 85951496; Tel: +86 532 85951496

^cKey Laboratory of Engineering Dielectrics and Its Application, Ministry of Education, Harbin University of Science and Technology, Harbin 150080, PR China


loss value can reach -34 dB with a sample thickness of just 1.5 mm. The composite can be regarded as an ideal microwave absorber.

2. Experimental

2.1 Sol-gel method for the synthesis of CF@CoFe₂O₄ composite

The CF@CoFe₂O₄ composite was facilely prepared by a sol-gel method. 2.7 g of FeCl₃·6H₂O, 1.2 g of CoCl₂·6H₂O and 0.5 g of CF were uniformly mixed with a moderate amount of C₆H₈O₇. After grinding the material into powder, the mixture was transferred into a flask maintained at 90 °C in a water bath and then 0.5 g ethylene was slowly added to the flask. Then, the pH of the reaction was adjusted to 8–9 by ammonia, after agitating for more than 180 min, the mixture became uniform and the gel was formed. Finally, the gel was calcined at 750 °C for 360 min under an N₂ atmosphere to obtain the CF@CoFe₂O₄ composite.^{29–31}

2.2 Preparation of the CF@CoFe₂O₄@MnO₂ composite

The CF@CoFe₂O₄@MnO₂ composite was facilely prepared *via* a hydrothermal reaction. 200 mg of the as-synthesized CF@CoFe₂O₄@MnO₂ composite was homogeneously distributed in 75 mL deionized water by high speed agitation for 1 h. Then, 1.5 mL hydrochloric acid and 1.0 g potassium permanganate were added successively.

After another 10 min of high-speed agitation, the liquid mixture was transferred into a 100 mL Teflon-lined stainless-steel autoclave and reacted at 150 °C for 120 min. After naturally cooling it to room temperature, the as-prepared CF@CoFe₂O₄@MnO₂ composite was separated *via* centrifugation at 10 000 rpm, successively washed with absolute ethanol for about 7–8 times, and put into a 100 °C blast drying oven for 12 h.^{32–35}

2.3 Characterization

The specimen morphology, structure, chemical and element compositions were determined *via* a scanning electron microscope (FESEM, Quanta600FEG) equipped with an energy dispersive X-ray (EDX) spectrometer. Besides, X-ray diffraction (XRD,

ESCALAB 250) in the 2 theta range of 10° < 2θ < 80° was adopted to measure the crystal structures of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites. The binding energy of the CF@CoFe₂O₄@MnO₂ composite was examined *via* X-ray photoelectron spectroscopy (XPS, Thermal Scientific Kα). The hysteresis loops of CoFe₂O₄, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites were characterized using a vibrating sample magnetometer (VSM, Lake Shore7307). For the microwave absorbing performance measurement, the complex permittivity (ε_r) and permeability (μ_r) of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites were investigated using an Agilent HP8720ES vector network analyzer in the frequency range of 2.0–18.0 GHz based on a coaxial method. First, the samples were uniformly distributed in a paraffin phase with the weight ratio of 30%, and then pressed into a cylindrical mold (φ_{in} = 3.04 mm, φ_{out} = 7.00 mm). Based on the obtained parameters of the samples, the corresponding reflection loss curves were further calculated and their microwave absorption performances could be identified.

3. Results and discussions

The preparation process of the CF@CoFe₂O₄@MnO₂ composite is briefly illustrated in Fig. 1. First, a typical sol-gel reaction was adopted to synthesize CF@CoFe₂O₄. Then, in order to make the MnO₂ nanocrystals *in situ* grow along the surface of the CF@CoFe₂O₄ composite, another hydrothermal reaction was carried out to complete the redox reaction of potassium permanganate and carbon, and the CF@CoFe₂O₄ composite was further coated with MnO₂ to obtain the CF@CoFe₂O₄@MnO₂ composite. The reactions occurring during the synthesis process are shown as eqn (1) and (2).^{36–39}



Fig. 2 exhibits the SEM images of CF (a), CF@CoFe₂O₄ (b), CF@CoFe₂O₄@MnO₂ composites (c) and the EDS spectra of CF@CoFe₂O₄@MnO₂ composite (d). It can be observed from

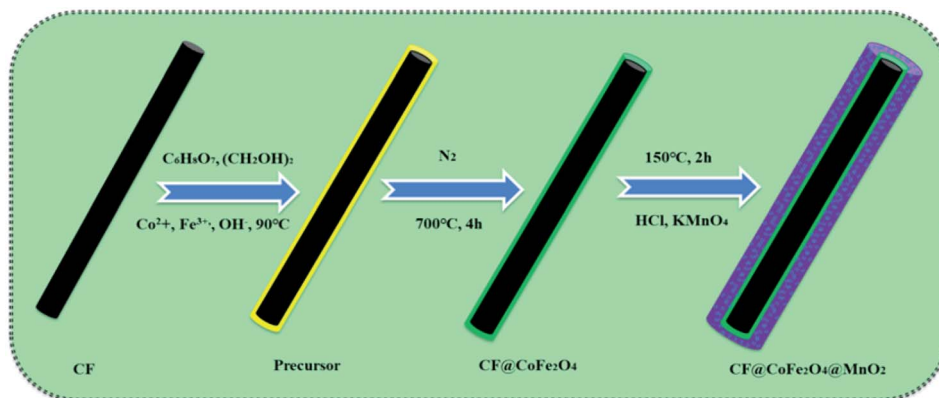


Fig. 1 Explanation of the preparation process of the CF@CoFe₂O₄@MnO₂ composite.





Fig. 2 SEM images of CF (a), CF@CoFe₂O₄ (b), CF@CoFe₂O₄@MnO₂ composites (c) and the EDS spectra of CF@CoFe₂O₄@MnO₂ composite (d).

the images that the pre-reaction carbon fiber possesses a smooth surface, and its diameter is about 6–7 μm. After the sol–gel reaction, the surface CF was homogeneously cladded by CoFe₂O₄ nanoparticles (Fig. 2b), and the thickness of overburden was about 600 nm. Fig. 2c reveals the morphology of the CF@CoFe₂O₄@MnO₂ composite, the CF@CoFe₂O₄ was uniformly coated with MnO₂ after the hydrothermal reaction, and the diameter further increased to around 8.2 nm. The total thickness of the coating layer could be calculated from the size difference (about 750 nm). The CF@CoFe₂O₄@MnO₂

composite's EDX patterns illustrate that the composite was composed of the elements of C, O, Mn, Fe and Co, the composition ratio (wt%) of these elements were 26.13%, 28.06%, 19.17%, 18.82% and 7.82%, respectively. The C element is mainly from the carbon fiber, while the O element can be attributed to the components of CoFe₂O₄ and MnO₂. The above results confirm the successful synthesis of the CF@CoFe₂O₄@MnO₂ composite. Meanwhile, the composite's EDX elemental mapping images (Fig. 3a–f) further identifies the components in the as-synthesized product.^{40–43}

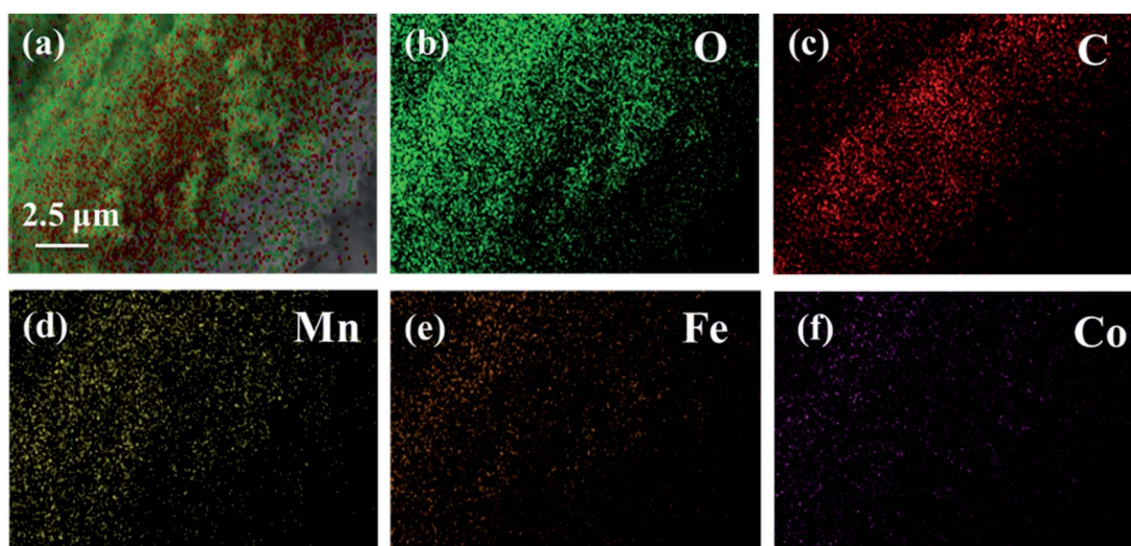


Fig. 3 EDX elemental mapping images (a–f) of CF@CoFe₂O₄@MnO₂ composite.





Fig. 4 XRD patterns of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites.

Fig. 4 displays the XRD patterns of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites, which can be used to investigate the samples' crystal structures. From this figure, the broad peak between 20°–40° represents the crystal plane diffraction peak of CF. After the sol-gel reaction, there are seven diffraction peaks located at $2\theta = 18.51^\circ, 30.41^\circ, 35.71^\circ, 43.5^\circ, 53.9^\circ, 57.5^\circ$ and 63° signifying the (1 1 1), (2 2 0), (3 1 1), (4 0 0), (4 2 2), (5 1 1) and (4 4 0) planes, respectively, of CoFe₂O₄ (JCPDS card no. 22-1086), in the XRD pattern of CF@CoFe₂O₄. Compared with the CF@CoFe₂O₄ sample, the additional two peaks of CF@CoFe₂O₄@MnO₂ composite located at 36.1° and



Fig. 6 Hysteresis loops of CoFe₂O₄, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites.

74.2° belong to MnO₂ crystal's (2 1 1) and (3 1 2) plane diffraction peaks, respectively, which can further confirm the successful synthesis of CF@CoFe₂O₄@MnO₂ composite.^{44–46}

Fig. 5 exhibits the XPS spectra of CF@CoFe₂O₄@MnO₂ composite. Fig. 5a is the survey scan spectra, from which the C 1s, Fe 2p, O 1s, Mn 2p, Co 2p binding energy can be observed. In Fig. 5b, the two peaks located at 283.5 eV and 284.6 eV are corresponding to the C–C/C=C and C–O binding energy of C element, respectively. The two peaks located at 711.5 eV and 726.4 eV represent Fe 2p_{3/2} and Fe 2p_{1/2} binding energies (Fig. 5c). From Fig. 5c, the 2p_{1/2} and 2p_{3/2} belonging to Mn element can obviously be observed. And the Co 2p_{3/2} and Co

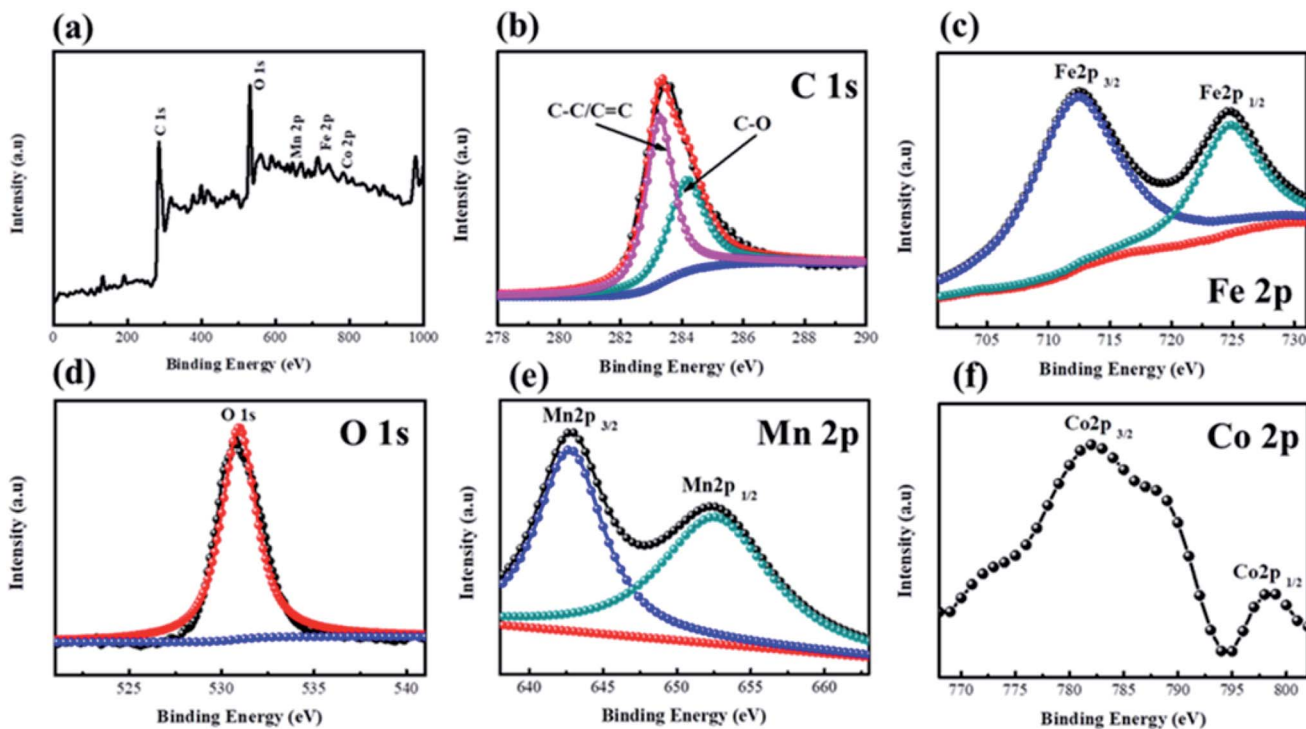


Fig. 5 XPS spectra of CF@CoFe₂O₄@MnO₂ composite, a survey scan (a), C 1s (b), Fe 2p (c), O 1s (d), Mn 2p (e), Co 2p (f).





Fig. 7 Electromagnetic parameters of CF (a), CF@CoFe₂O₄ (b) and CF@CoFe₂O₄@MnO₂ composite (c).

2p_{1/2} binding energy peaks are located at 782.8 eV and 798.2 eV, respectively, which can be observed in Fig. 5f. The above results jointly verified the elemental composition of the as-synthesized CF@CoFe₂O₄@MnO₂ composite.^{47–50}

In view of the magnetic loss mechanism of electromagnetic waves, the magnetic behaviors of microwave absorbers have a great effect on their microwave absorbing performance, thus the magnetic hysteresis loops of CoFe₂O₄, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites were measured by utilizing VSM and the results are exhibited in Fig. 6. The CoFe₂O₄, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites all displayed a typical soft magnetic behavior, which is very beneficial for the absorption of microwaves. The magnetic saturation values of CoFe₂O₄, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites were 65.5 emu g⁻¹, 54.8 emu g⁻¹ and 30.2 emu g⁻¹, respectively. The reduction in their magnetic saturation can mainly be attributed to the decrease of the mass ratio of the unique magnetic material CoFe₂O₄ among these samples.

Normally, when the microwave is incident upon the surface of the sample, it would be reflected or transmitted, meanwhile, the contained microwave energy would be absorbed by magnetic loss and dielectric loss or transformed into heat energy and scattered in the air. In view of the loss mechanism of the microwave, the absorption mode of the microwave can mainly be divided into magnetic loss and dielectric loss, which can be calculated by utilizing its permeability μ' , μ'' and

permittivity ϵ' , ϵ'' , respectively. The parameter's real part μ' and ϵ' represent the storage capability of a material, while the imaginary part μ'' and ϵ'' on behalf of the dissipation capability of magnetic energy and electric energy, respectively. Based on μ' , μ'' , ϵ' and ϵ'' , the corresponding reflection loss patterns of the measured samples can be calculated by using eqn (3)–(6).^{51–57}

$$\Gamma = \frac{Z_{in} - Z_0}{Z_{in} + Z_0} \quad (3)$$

$$Z_0 = (\mu_0/\epsilon_0)^{1/2} \quad (4)$$

$$Z_{in} = Z_0 \left(\sqrt{\frac{\mu_r}{\epsilon_r}} \tanh \left[j \left(\frac{2\pi f d}{c} \right) (\sqrt{\mu_r \epsilon_r}) \right] \right) \quad (5)$$

$$R_L = 20 \log \left(\frac{Z_{in} - Z_0}{Z_{in} + Z_0} \right) \quad (6)$$

In these formulas, Z_{in} represents normalized input impedance of the absorbing material, Z_0 on behalf of the impedance of free space, parameter d stands for the thickness of absorber, parameter c means the light velocity in the vacuum and another parameter f signifies the frequency of the input microwave. Thus, the measured sample's thickness possesses a great effect on its microwave absorption performance. In addition, the absorbers' microwave absorption performances were mainly codetermined by their magnetic property and dielectric property. The



Fig. 8 Dielectric loss (a) and magnetic loss (b) of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites.





Fig. 9 Reflection loss curves of CF (a), CF@CoFe₂O₄ (b) and CF@CoFe₂O₄@MnO₂ composite (c) at a different thickness, the effective absorption band width of CF@CoFe₂O₄@MnO₂ composite (d).

electromagnetic parameters of CF, CF@CoFe₂O₄ and CF@CoFe₂O₄@MnO₂ composites are exhibited in Fig. 7, and the corresponding dielectric loss ($\tan \delta_e = \epsilon''/\epsilon'$) and magnetic loss ($\tan \delta_m = \mu''/\mu'$) were also calculated and shown in Fig. 8. By comparing the three samples' electromagnetic parameters, as a conductive material, the CF sample possesses high dielectric parameter value (real part ~ 16 and imaginary part ~ 7). However, as a nonmagnetic material, the magnetic parameter values of CF are the lowest among these samples (real part ~ 1 and imaginary part ~ 0), which is unfavorable to the magnetic loss for electromagnetic waves. After the sol-gel reaction, the dielectric parameter values and $\tan \delta_e$ of CF@CoFe₂O₄ decreased while its magnetic parameters (real part, imaginary part and magnetic loss) were all increased, which can mainly be attributed to the introduction of magnetic material CoFe₂O₄. Compared with CF@CoFe₂O₄, the CF@CoFe₂O₄@MnO₂ composite's magnetic loss was reduced, while the dielectric loss was improved (real part ~ 10.8 and imaginary part ~ 3.2), which can result in a more reasonable electromagnetic matching, further enhancing the sample's microwave absorbing performance. Besides, the CF@CoFe₂O₄ sample the CF@CoFe₂O₄@MnO₂ composite sample exhibited resonance phenomenon, which is considered to be associated with local confinement, natural resonance and exchange resonance loss.⁵⁸⁻⁶²

According to the measured ϵ' , ϵ'' , μ' , μ'' , the reflection loss patterns at different thicknesses ranging from 2–18 GHz of CF

(a), CF@CoFe₂O₄ (b) and CF@CoFe₂O₄@MnO₂ composite (c) samples were calculated and the results are exhibited in Fig. 8. As shown in Fig. 8a, as a nonmagnetic material, the EM wave absorbing capacity of a pure carbon fiber is poor and its minimum reflection loss ($R_{L \min}$) value is -15 dB with a specimen thickness of 1.6 mm. However, when combined with magnetic material CoFe₂O₄ *via* the sol-gel method, the CF@CoFe₂O₄, its microwave absorbing performance was enhanced, and the minimum reflection loss value is less -20



Fig. 10 Mechanism illustration of microwave absorption for the CF@CoFe₂O₄@MnO₂ composite.



Table 1 The electromagnetic wave absorbing performance for analogous absorbers

Sample	Frequency range (GHz)	Weight percent of filler	Adhesive	Thickness	$R_{L \min}$	EAB width (GHz)	Reference
Fe ₃ O ₄ @C@MnO ₂	2–18	30%	Paraffin wax	2.7 mm	–35 dB	5.0	28
CNT/CoFe ₂ O ₄	2–18	N.A	N.A	1.4 mm	–18 dB	7.0	46
PANI/MnO ₂ /CF	8.2–12.4	30%	Paraffin wax	2.5 mm	–22 dB	3.0	61
NiFe ₂ O ₄ @MnO ₂	2–18	30%	Paraffin wax	2.0 mm	–25 dB	2.7	33
Carbonyl iron/MnO ₂	2–18	30%	Paraffin wax	3.5 mm	–39.1 dB	3.0	58
PANI@Ni@CF	8.2–12.4	20%	Paraffin wax	2.0 mm	–12.4 dB	1.2	42
α -Fe ₂ O ₃ @CoFe ₂ O ₄	2–18	30%	Paraffin wax	2.5 mm	–41 dB	5.0	59
CF@CoFe ₂ O ₄ @MnO ₂	2–18	30%	Paraffin wax	1.5 mm	–34 dB	5.0	This work

dB, which can mainly be attributed to the enhancement of magnetic loss. When further combined with MnO₂, the CF@CoFe₂O₄@MnO₂ composite possesses a strong microwave absorbing capacity, which can reach up to –41 dB, far higher than the CF and CF@CoFe₂O₄ samples. The effective absorption bandwidth (EAB) of CF@CoFe₂O₄@MnO₂ composite is shown in Fig. 9d, it can obviously be observed that when the sample thickness is just 1.5 mm, its minimum reflection loss value and EAB value can reach –34 dB and 5 GHz, respectively, indicating that the composite can achieve high absorption efficiency and wide EAB under a small thickness, which is very beneficial for further applications.^{63–65}

The above results illustrate that the as-synthesized CF@CoFe₂O₄@MnO₂ composite exhibits superior microwave absorption performance both in absorbing efficiency and EAB width with a low thickness. The mechanism sketch illustration of microwave absorption for the CF@CoFe₂O₄@MnO₂ composite is shown in Fig. 10. First, the dielectric material CF, MnO₂ and magnetic material CoFe₂O₄ can achieve fair electromagnetic matching. Second, the multiple interfaces that emerged from its layer-by-layer cladding structure can increase absorption times of EM wave. Third, the interfacial polarizations and interface relaxation between MnO₂ and NiFe₂O₄ can further enhance its microwave capacity. These factors code-termined the excellent microwave absorbing properties of the CF@CoFe₂O₄@MnO₂ composite.^{66–71} When compared with other reported homologous microwave absorber including Fe₃O₄@C@MnO₂,²⁸ CNT/CoFe₂O₄,⁴⁶ PANI/MnO₂/CF,⁶¹ NiFe₂O₄@MnO₂,³³ carbonyl iron/MnO₂,⁵⁸ PANI@Ni@CF⁴² and α -Fe₂O₃@CoFe₂O₄ (ref. 59) (Table 1), the as-synthesized CF@CoFe₂O₄@MnO₂ composite showed excellent EM wave absorption performance.

4. Conclusion

In summary, a uniform CF@CoFe₂O₄@MnO₂ composite was facilely fabricated *via* a two-step method, a sol-gel method and a hydrothermal reaction. The morphology, structure, chemical and element composition, crystal form, elemental binding energy, magnetic behavior, and microwave absorbing performances of the composite were carefully investigated. According to its hysteresis loops, the composite exhibited a typical soft magnetic behavior, with an M_s value of 30.2 emu g^{–1}. Besides,

the as-synthesized CF@CoFe₂O₄@MnO₂ composite possesses superior microwave absorption performance mainly due to a reasonable electromagnetic matching, and its minimum reflection loss value can reach –34 dB with a sample thickness of just 1.5 mm. The composite can be regarded as an ideal microwave absorber.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

This work was financially supported by the Natural Science Foundation of Shandong Province (ZR2019YQ24), the Qingchuang Talents Induction Program of Shandong Higher Education Institution (Research and Innovation Team of Structural-Functional Polymer Composites), National Natural Science Foundation of China (51407134, 51801001), China Postdoctoral Science Foundation (2016M590619, 2016M601878), Qingdao Postdoctoral Application Research Project, Key Laboratory of Engineering Dielectrics and Its Application (Harbin University of Science and Technology), Ministry of Education (KFZ1803), Provincial Key Research and Development Program of Shaanxi (2019GY-197), Key Project of Baoji University of Arts and Sciences (ZK2018051), Baoji Science and Technology Project (16RKX1-29) and Baoji Engineering Technology Research Center for Ultrafast Optics and New Materials (2015CXNL-1-3). Feng AL is supported by The Thousand Talents Plan for Young Professionals of Shaanxi Province.

References

- H. L. Lv, Z. H. Yang, S. J. H. Ong, C. Wei, H. B. Liao, S. B. Xi, Y. H. Du, G. B. Ji and Z. C. J. Xu, *Adv. Funct. Mater.*, 2019, **29**, 1900163.
- H. L. Xu, X. W. Yin, X. L. Li, M. H. Li, S. Liang, L. F. Cheng and L. T. Zhang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 10198–10207.
- C. Cheng, Z. Chen, Z. Huang, C. Zhang, R. Tusiime, J. Zhou, Z. Sun, Y. Liu, H. Zhang and M. Yu, *Composites, Part A*, 2020, **129**, 105696.



- 4 C. Liang, H. Qiu, P. Song, X. Shi, J. Kong and J. Gu, *Sci. Bull.*, 2020, DOI: 10.1016/j.scib.2020.02.009.
- 5 X. Chen, T. Shi, K. Zhong, G. Wu and Y. Lu, *Chem. Eng. J.*, 2020, **379**, 122240.
- 6 S. Chen, G. Meng, B. Kong, B. Xiao, Z. Wang, Z. Jing, Y. Gao, G. Wu, H. Wang and Y. Cheng, *Chem. Eng. J.*, 2020, **387**, 123662.
- 7 A. Feng, G. Wu, C. Pan and Y. Wang, *J. Nanosci. Nanotechnol.*, 2017, **17**, 3786–3791.
- 8 Y. Wang, K. Kou and L. Zhuo, *RSC Adv.*, 2016, 5(72), 58821–58831.
- 9 B. Zhao, J. Deng, C. Zhao, C. Wang, Y. Chen, M. Hamidinejad, R. Li and C. Park, *J. Mater. Chem. C*, 2020, **8**, 58.
- 10 C. Liang, P. Song, H. Qiu, Y. Zhang, X. Ma, F. Qi, H. Gu, J. Kong and J. Gu, *Nanoscale*, 2019, **11**, 22590–22598.
- 11 H. Zhang, Z. Jia, A. Feng, Z. Zhou, C. Zhang, K. Wang and N. Liu, *Compos. Commun.*, 2020, DOI: 10.1016/j.coco.2020.02.010.
- 12 P. Song, H. Qiu, L. Wang, X. Liu, Y. Zhang, J. Zhang, J. Kong and J. Gu, *Sustainable Mater. Technol.*, 2020, DOI: 10.1016/j.susmat.2020.e00153.
- 13 J. Li, J. Ma, S. Chen, Y. Huang and J. He, *Mater. Sci. Eng., C*, 2018, **89**, 25–32.
- 14 C. Zhang, K. Zeng, C. Wang, X. Liu, G. Wu, Z. Wang and D. Wang, *Ceram. Int.*, 2020, **46**, 6652–6662.
- 15 A. Feng, T. Hou, Z. Jia, Y. Zhang and F. Zhang, *Nanomaterials*, 2020, **10**, 162.
- 16 Z. Wang, M. Yang, Y. Cheng, J. Liu, B. Xiao, S. Chen, J. Huang and Q. Xie, *Composites, Part A*, 2019, **118**, 302–311.
- 17 G. Wu, Z. Jia, Y. Cheng, H. Zhang, X. Zhou and H. Wu, *Appl. Surf. Sci.*, 2019, **10**, 472–478.
- 18 H. Lv, X. Liang, G. Ji, H. Zhang and Y. Du, *ACS Appl. Mater. Interfaces*, 2015, **7**, 9776–9783.
- 19 Y. Cheng, J. M. Cao, Y. Li, Z. Y. Li, H. Q. Zhao, G. B. Ji and Y. W. Du, *ACS Sustainable Chem. Eng.*, 2018, **6**, 1427–1435.
- 20 X. Liang, B. Quan, B. Sun, Z. Man, X. Xu and G. Ji, *ACS Sustainable Chem. Eng.*, 2019, **7**, 10477–10483.
- 21 B. Quan, W. Shi, S. J. H. Ong, X. Lu, P. L. Wang, G. Ji and Z. J. Xu, *Adv. Funct. Mater.*, 2019, **29**(28), 1901236.
- 22 X. Cui, X. Liang, J. Chen, W. Gu, G. Ji and Y. Du, *Carbon*, 2020, **156**, 49–57.
- 23 S. K. Singh, M. J. Akhtar and K. K. Kar, *Composites, Part B*, 2019, **167**, 135–146.
- 24 P. Liu, Y. Huang and X. Zhang, *Powder Technol.*, 2015, **276**, 112–117.
- 25 P. Chamoli, S. K. Singh, M. J. Akhtar, M. K. Das and K. K. Kar, *Phys. E*, 2018, **103**, 25–34.
- 26 Y. Wang, K. Kou, C. Pan and A. Feng, *J. Mater. Sci.: Mater. Electron.*, 2016, **27**(8), 8279–8287.
- 27 H. Wu, Z. Zhao and G. Wu, *J. Colloid Interface Sci.*, 2020, **566**, 21–32.
- 28 X. L. Chen, Z. R. Jia, A. L. Feng, B. B. Wang, X. H. Tong, C. H. Zhang and G. L. Wu, *J. Colloid Interface Sci.*, 2019, **553**, 465–474.
- 29 S. K. Singh, H. Prakash, M. J. Akhtar and K. K. Kar, *ACS Sustainable Chem. Eng.*, 2018, **6**(4), 5381–5393.
- 30 Z. Jia, C. Wang, A. Feng, P. Shi, C. Zhang, X. Liu and K. Wang, *Composites, Part B*, 2020, **183**, 107690.
- 31 Y. Wang, X. Gao, L. Zhang, X. Wu, Q. Wang and C. Luo, *Appl. Surf. Sci.*, 2019, **480**, 830–838.
- 32 X. Zhou, Z. Jia, X. Wang, J. Liu, M. Zhang and H. Cao, *Carbon*, 2019, **152**, 827–836.
- 33 Z. R. Jia, B. B. Wang, A. L. Feng, J. Liu, M. Zhang and Z. Huang, *J. Alloys Compd.*, 2019, **799**, 216–223.
- 34 A. Feng, M. Ma, Z. Jia and M. Zhang, *RSC Adv.*, 2019, **9**, 25932–25941.
- 35 H. Yan, X. Xue, Y. Fu and X. Wu, *Ceram. Int.*, 2019, DOI: 10.1016/j.ceramint.2019.12.241.
- 36 K. Nasouri and A. M. Shoushtari, *Compos. Sci. Technol.*, 2017, **145**, 46–54.
- 37 T. Hou, B. Wang, M. Ma, A. Feng, Z. Huang, Y. Zhang, Z. Jia, G. Tan and H. Cao, *Composites, Part B*, 2020, **180**, 107577.
- 38 G. Wu, Y. Cheng, Z. Yang, Z. Jia, H. Wu, L. Yang, H. Li and P. Guo, *Chem. Eng. J.*, 2018, **333**, 519–528.
- 39 A. Feng, G. Wu, C. Pan and Y. Wang, *J. Nanosci. Nanotechnol.*, 2017, **17**, 3859–3863.
- 40 W. Wu, C. Yu, J. Chen and Q. Yang, *Int. J. Environ. Anal. Chem.*, 2020, **100**, 324–332.
- 41 H. L. Xu, X. W. Yin, M. Zhu, M. H. Li, H. Zhang, H. J. Wei, L. T. Zhang and L. F. Cheng, *Carbon*, 2019, **142**, 346–353.
- 42 X. L. Chen, X. W. Wang, L. D. Li and S. H. Qi, *J. Mater. Sci.: Mater. Electron.*, 2016, **27**, 5607–5612.
- 43 W. Wu, C. Yu, Q. Wang, F. Zhao, H. He, C. Liu and Q. Yang, *Crit. Rev. Food Sci. Nutr.*, 2019, DOI: 10.1080/10408398.2019.1636763.
- 44 F. Zhang, Z. Jia, C. Wang, A. Feng, T. Hou, K. Wang, J. Liu, Y. Zhang and G. Wu, *Energy*, 2020, **19**, 117047.
- 45 Z. Jia, B. Wang, A. Feng, J. Liu, C. Zhang, M. Zhang and G. Wu, *Ceram. Int.*, 2019, **13**, 15854–15859.
- 46 B. Zhao, J. Liu, X. Guo, W. Zhao, L. Liang, C. Ma and R. Zhang, *Phys. Chem. Chem. Phys.*, 2017, **19**, 9128–9136.
- 47 H. Lv, Z. Yang, P. Wang, G. Ji, J. Song, L. Zheng, H. Zeng and Z. Xu, *Adv. Mater.*, 2018, **30**, 1706343.
- 48 D. Lan, M. Qin, R. Yang, S. Chen, H. Wu, Y. Fan, Q. Fu and F. Zhang, *J. Colloid Interface Sci.*, 2019, **533**, 481–491.
- 49 H. Zhang, B. Wang, A. Feng, N. Zhang, Z. Jia, Z. Huang and X. Liu, *Composites, Part B*, 2019, **167**, 690–699.
- 50 Y. Wang, Y. Fu, X. Wu, W. Zhang, Q. Wang and J. Li, *Ceram. Int.*, 2017, **43**, 11367–11375.
- 51 G. Wu, Z. Jia, X. Zhou and G. Nie, *Composites, Part A*, 2020, **128**, 105687.
- 52 B. Quan, W. Liu, G. Xu, G. Ji and Y. Du, *J. Colloid Interface Sci.*, 2019, **543**, 138–146.
- 53 X. Chen, K. Zhong, T. Shi, X. Meng and Y. Lu, *Synth. Met.*, 2019, **248**, 59–67.
- 54 G. Wu, H. Zhang, X. Luo, L. Yang and H. Lv, *J. Colloid Interface Sci.*, 2019, **536**, 548–555.
- 55 Z. Gao, Z. Jia, J. Zhang, A. Feng and Z. Huang, *J. Mater. Sci.: Mater. Electron.*, 2019, **30**, 13474–13487.
- 56 S. Gao, S. Yang, H. Wang, G. Wang and P. Yin, *Carbon*, 2020, DOI: 10.1016/j.carbon.2020.02.031.



- 57 T. Q. Hou, B. B. Wang, Z. R. Jia, H. J. Wu, D. Lan, Z. Y. Huang, A. L. Feng and M. L. Ma, *J. Mater. Sci.: Mater. Electron.*, 2019, **30**, 10961–10984.
- 58 Z. Lou, R. Li, P. Wang, Y. Zhang, B. Chen, C. Huang, C. Wang, H. Han and Y. Li, *Chem. Eng. J.*, 2019, DOI: 10.1016/j.cej.2019.123571.
- 59 H. Lv, X. Liang, Y. Cheng, H. Zhang, D. Tang, B. Zhang, G. Ji and Y. Du, *ACS Appl. Mater. Interfaces*, 2015, **7**, 4744–4750.
- 60 X. Zhou, C. Zhang, M. Zhang, A. Feng, S. Qu, Y. Zhang and X. Liu, *Composites, Part A*, 2019, **127**, 105627.
- 61 M. Qin, D. Lan, X. Qiao and H. Wu, *Appl. Surf. Sci.*, 2020, **504**, 144480.
- 62 S. Chen, Y. Cheng, Q. Xie, B. Xiao and Z. Wang, *Composites, Part A*, 2019, **120**, 84–94.
- 63 Z. Lou, C. Yuan, Y. Zhang, Y. Li and J. Cai, *J. Alloys Compd.*, 2019, **775**, 800–809.
- 64 J. Liu, H. Liang, Y. Zhang, G. Wu and H. Wu, *Composites, Part B*, 2019, **176**, 107240.
- 65 Z. Gao, B. Xu, M. Ma, A. Feng, Y. Zhang, X. Liu and Z. Jia, *Composites, Part B*, 2019, **179**, 107417.
- 66 F. Alanagha, A. Khiabanib and A. Asl, *Compos. Sci. Technol.*, 2017, **150**, 65–78.
- 67 Z. Jia, K. Kou, S. Yin, A. Feng, C. Zhang, X. Liu and H. Cao, *Composites, Part B*, 2020, **189**, 107895.
- 68 H. Lv, Z. Yang, H. Xu, L. Wang and R. Wu, *Adv. Funct. Mater.*, 2020, **30**, 1907251.
- 69 H. Zhao, L. Hou, S. Bi and Y. Lu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 33059–33070.
- 70 D. Lan, M. Qin, J. L. Liu, Y. Zhang and H. Wu, *Chem. Eng. J.*, 2020, **382**, 122797.
- 71 L. Long, E. Yang, X. Qi, R. Xie, Z. Bai, S. Qin, C. Deng and W. Zhong, *ACS Sustainable Chem. Eng.*, 2020, **8**, 613–623.

