

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/chemicalscience

ARTICLE

Solid-State Principles Applied to Organic-Inorganic Perovskites: New Tricks for an Old Dog

Cite this: DOI: 10.1039/x0xx00000x

Gregor Kieslich, Shijing Sun and Anthony K. Cheetham*

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Hybrid organic-inorganic materials that adopt perovskite-like architectures show intriguing order-disorder phase transitions and exciting electronic properties. We extend the classical concept of ionic Tolerance Factors to this important class of materials and predict the existence of several hitherto undiscovered hybrid perovskite phases.

Introduction

Perovskites of general formula ABX_3 have played a central role in the evolution of materials chemistry and condensed matter physics over the last 70 years. The development of perovskite oxides ABO_3 has been particularly significant and they are used in a wide range of applications such as ferroelectrics, high-temperature superconductors, and giant magnetoresistance devices.¹ It is exciting to observe, therefore, that a new class of hybrid organic-inorganic perovskites is now attracting the attention of chemists and physicists, and is making remarkable strides in fields such as multiferroics and thin-film solar cells. The present contribution explores the extent to which learning from the literature on oxide perovskites can be applied towards the discovery of new organic-inorganic analogues.

Hybrid organic-inorganic frameworks, which include the wide family of metal-organic frameworks (MOFs), have evolved over the last 15 years into one of the fastest growing research fields in materials science. The unlimited combinations of metal ions and organic linkers, which give rise to enormous structural and chemical diversity,^{2,3} enable the targeted design of materials for many applications. Most of the research on MOFs hitherto has concerned *porous* systems, which are being explored for applications in gas storage,⁴ chemical sensing,⁵ biomedicine⁶ and catalysis.⁷ There is growing interest, however, in *dense* MOFs, which show potential for applications in many other areas, such as optical devices, batteries and semiconductors.⁸ A subset of these dense hybrid frameworks adopt the perovskite architecture and exhibit a remarkable range of properties. In ABX_3 formates such as $[AmH]M(HCOO)_3$ (A = protonated amine, $[AmH]^+$, $B = M^{2+}$ and $X = HCOO^-$), the divalent metal cation occupies BO_6 octahedra which are linked by formate bridges to form a pseudo-cubic ReO_3 -like cavity. The amine cation, which is located in the perovskite cavity (Fig. 1a), is often disordered at

ambient temperatures and the systems show an fascinating range of ferroelectric and multiferroic properties on cooling.^{9–11} A second class of hybrid perovskites of general composition $[AmH]MX_3$ ($M = Sn^{2+}, Pb^{2+}$ and $X = Cl^-, Br^-, I^-$)¹² has attracted a great deal of attention recently. In particular, lead based iodides show impressive performances in solar cell applications and take advantage of straightforward processing methods such as spin-coating, dip-coating and vapour deposition techniques.^{13,14} Their electrical power conversion efficiencies, although sensitive to measurement parameters, have increased from 3.8% in 2009¹⁵ to over 15% by the end of 2013^{13,16,16a} leading to a surge of interest in the study of hybrid perovskites.

The complex interplay between different types of bonding interactions makes crystal engineering of hybrid perovskites a challenging task, even though some important studies have addressed this issue.^{18,19} Inspired by Mitzi's 2001 work,¹⁸ the present study explores the extent to which learnings from inorganic perovskites can be applied quantitatively to their hybrid analogues.

The Tolerance Factor

In 1926, V.M. Goldschmidt introduced a geometrical parameter α , the so-called Tolerance Factor, to evaluate ionic size mismatches which the perovskite-structure will tolerate until a different structure-type is formed, see eq. (1):²⁰

$$\alpha = (r_A + r_X) / \sqrt{2}(r_B + r_X), \quad (1)$$

with r_i being the radii of ions in the perovskite ABX_3 , and $i = A, B$ and X , respectively. Eq. (1) is a semi-empirical relationship that combines the idea of dense ionic packing with early estimates of ionic radii; it continues to be widely used as a guiding principle in the study of oxide perovskites. For values of α in the range 0.9 – 1.0, mostly cubic perovskites are found, whereas values of 0.80 – 0.89 predominantly lead to distorted

perovskites which can be further classified by using Glazer's concept of octahedral tilting.²¹ Below ~ 0.80 , other structures such as the ilmenite-type (FeTiO_3) are more stable due to the similar sizes of the cations A and B . Values of α larger than 1 lead to hexagonal structures where layers of face-sharing octahedra are introduced into the structure.

Tolerance Factors of Hybrid Frameworks

The challenge in determining Tolerance Factors for organo-inorganic compounds lies in estimating the ionic radii of molecular ions. This problem has been addressed in the past and a set of thermochemical radii for molecular anions was proposed by Kapustinskii and Yatsimirskii in the 1940s.²² In the case of hybrid perovskites we are dealing with molecular cations, where varying bond lengths due to hydrogen-bonding interactions make it difficult to define an ionic radius. Even highly symmetrical cations, such as $[\text{NH}_4]^+$ and $[(\text{CH}_3)_4\text{N}]^+$, exhibit radii which depend significantly on their anionic counterparts,²³ making Tolerance Factors for hybrid perovskites a challenging problem. In 2001 Mitzi applied eq. 1 to the hybrid lead iodides and obtained a maximum radius for the protonated amines of $\sim 260\text{pm}$.¹⁸ In the present work we expand on this initial work and also extend the Tolerance Factor concept to the formate perovskites. We use crystallographic data from known perovskite-like hybrid frameworks to estimate a consistent set of effective radii for different organic ions. In particular, assuming free rotational freedom around the centre of mass, a rigid sphere model is applicable to organic cations (Fig. 1a) and leads to a consistent set of effective ionic radii, r_{Aeff} . We have used eq. (2) to suggest effective ionic radii for the most common nitrogen based cations, Table 1.

$$r_{\text{Aeff}} = r_{\text{mass}} + r_{\text{ion}}, \quad (2)$$

with r_{mass} being the distance between the centre of mass of the molecule and the atom with the largest distance to the centre of mass, excluding hydrogen atoms; r_{ion} is the corresponding ionic radius of this atom.²¹ For example, in case of the guanidinium cation we found $r_{\text{mass}} = r(\text{C-N}) = 132\text{ pm}$ and $r_{\text{ion}} = r(\text{N}^{3-}) = 146\text{ pm}$; therefore according to eq. (2) $r_{\text{Aeff}} = 278\text{ pm}$. This approach gives a set of effective radii that can be used to estimate Tolerance Factors. For molecular anions such as HCOO^- , CN^- and N_3^- , the situation is complicated by the high anisotropy of the anion. We have therefore treated all molecular anions as rigid cylinders, with effective radius r_{Xeff} and an effective height h_{Xeff} , see Figure 1b (yellow cylinders). The radius and the height of the cylinder are then evaluated according eq. (2). Equation (1) is then modified to give eq. 3:

$$\alpha = (r_{\text{Aeff}} + r_{\text{Xeff}}) / \sqrt{2}(r_{\text{B}} + 0.5h_{\text{Xeff}}), \quad (3)$$

Table 1. Effective radii of molecular cations and anions. Ionic radii of divalent metal ions were used according Ref. 21.

Cation	Effective Radius r_{Aeff} (pm)
1 Ammonium $[\text{NH}_4]^+$	146
2 Hydroxylammonium $[\text{H}_3\text{NOH}]^+$	216
3 Methylammonium $[(\text{CH}_3)\text{NH}_3]^+$	217
4 Hydrazinium $[\text{H}_3\text{N-NH}_2]^+$	217
5 Azetidinium $[(\text{CH}_2)_3\text{NH}_2]^+$	250
6 Formamidinium $[\text{NH}_2(\text{CH})\text{NH}_2]^+$	253
7 Imidazolium $[\text{C}_3\text{N}_2\text{H}_5]^+$	258
8 Dimethylammonium $[(\text{CH}_3)_2\text{NH}_2]^+$	272
9 Ethylammonium $[(\text{C}_2\text{H}_5)\text{NH}_3]^+$	274
10 Guanidinium $[\text{C}(\text{NH}_2)_3]^+$	278
11 Tetramethylammonium $[(\text{CH}_3)_4\text{N}]^+$	292

Anions	r_{Xeff}	h_{Xeff}
Iodide, I^-	$r_{\text{Xeff}} = 220$	
Formate, HCOO^-	$r_{\text{Xeff}} = 136$	$h_{\text{Xeff}} = 447$

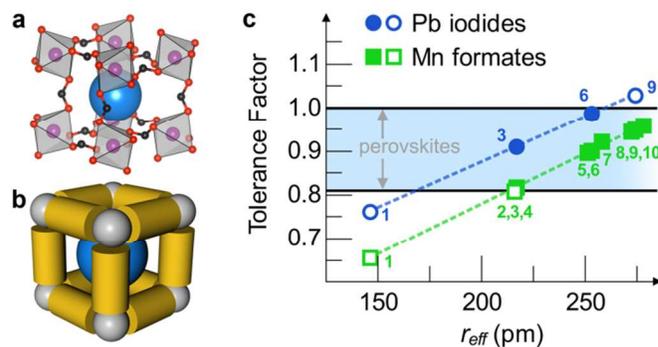


Figure 1. A strong correlation exists between Tolerance Factors and underlying crystal structures and all currently known perovskite MOFs exhibit tolerance factors between 0.81 and 1.01. **a**, Structure and polyhedral connectivity of $[(\text{CH}_3)_2\text{NH}_2]\text{Mn}(\text{HCOO})_3$ to highlight the perovskite-like architecture. Hydrogen atoms are omitted and atomic radii are chosen for clarity; purple: manganese, red: oxygen, black: carbon and blue: $[(\text{CH}_3)_2\text{NH}_2]^+$. **b**, Schematic of the model that is used for the calculation of the tolerance factors of formates. **c**, tolerance factors of Pb iodides (circles) and Mn formates (squares) plotted versus cation size. Open symbols indicate reported compounds with a non-perovskite structure. The light blue area highlights the range where perovskite-like frameworks are expected to form. The uncertainty in the tolerance factors is estimated to be 6%.

In Figure 1c, Tolerance Factors of the hybrid Pb iodides and Mn formates calculated according to eq. (2) and (3), are plotted as a function of the A cation radius. The larger ReO_3 cavity of the formates leads to a horizontal shift of the critical cation sizes for perovskite formation to larger A cation radii, $r_{\text{Aeff}} = 168\text{--}259\text{ pm}$ (iodides) and $r_{\text{Aeff}} = 213\text{--}295\text{ pm}$ (formates). The maximum cation size for iodides is in excellent agreement with previous reported result, $r_{\text{Aeff}} \sim 260\text{ pm}$.¹⁸

Currently, nearly all reported hybrid frameworks with an ABX₃ perovskite-like structure exhibit Tolerance Factors between 0.81 and 1.01; in other words, the relative packing density of MOFs plays a crucial role in the formation of hybrid frameworks with the perovskite structure, which include perovskite-like cyanides and structurally flexible ABX₃ azide frameworks.^{24,25,26} Although the complexity of the hybrid systems leads us to expect that more exceptions will be discovered in the future, and clearly the exact boundaries are subject to uncertainty due to inaccuracies relating to r_{eff} , the relationship between hybrid perovskites and their solid-state analogues is remarkably strong. For example, with decreasing size of the cation A, the relative density of the perovskite-formates steadily decreases until around $\alpha = 0.81$, where an unusual chiral structure becomes energetically comparable to the perovskite-type architecture.²⁷ Both polymorphs have been observed for [NH₂NH₃]M(HCOO)₃ (M = Mn, Zn, Co, Mg) and the synthetic procedure appears to determine which phase forms.²⁸ It will be interesting to see if both polymorphs can be stabilized at room temperature and (reversible) pressure-driven phase transitions occur.

So far, the upper limit of Tolerance Factors where a pseudo-cubic perovskite-structure is expected to form is well defined. Similar to the perovskite oxides, [(C₂H₅)NH₃]PbI₃ ($\alpha = 1.05(4)$) adopts an hexagonal structure with 1D chains of face-sharing PbI₆ octahedra. Such structural motifs are absent in formate based compounds due to the face-sharing connectivity. However, an interesting case where the Tolerance Factor concept does not seem to apply is found for the guanidinium tin chlorides and bromides. In such compounds, a stereochemically active lone pair leads to heavily distorted perovskite structures. For example, three short Sn-Cl distances (~2.5 Å) are observed in [(NH₂)₃C]SnCl₃, whereas the other three Sn-Cl bonds (between 3.2 Å and 3.7 Å) are elongated due to repulsion effects between the tin lone pairs and the halide ions.^{29,30} The structure is therefore better described as containing SnCl₃⁻ anions, rather than the SnCl₆ octahedra required by the perovskite structure. As a consequence, use of the Tolerance Factor concept becomes inappropriate.

Based on the considerations presented above, we can predict the existence of three hitherto unknown perovskite-like compounds: [H₃NOH]PbI₃ ($\alpha = 0.90(9)$), [N₂H₅]PbI₃ ($\alpha = 0.91(2)$) and [(CH₂)₃NH₂]PbI₃ ($\alpha = 0.98(0)$). A fourth compound, [C₃N₂H₅]PbI₃ has a tolerance factor close to the borderline ($\alpha = 0.99(7)$) and is likely to exist in a perovskite structure. The preparation of hydroxylammonium and hydrazinium based compounds is particularly exciting (although experimentally challenging) as they exhibit similar tolerance factors as the high-efficient photovoltaic material [(CH₃)NH₃]PbI₃ ($\alpha = 0.91(2)$). A further predicted compound, [NH₂(CH₂)NH₂]Mn(HCOO)₃, was reported during writing this paper,³¹ underlining the utility of our concept.

Conclusion

In conclusion, we have defined a consistent set of effective ionic radii for organic and molecular ions which we then used to estimate Tolerance Factors for organic-inorganic hybrid perovskites of lead iodides and manganese formates. The methodology is also applicable to related hybrid families, for example cyanides and azides, and the excellent agreement between calculated Tolerance Factors and experimental structural observations bodes well for future efforts to identify promising amine-metal-anion combinations. So far, the limitations of Tolerance Factors for hybrid materials are not yet clear, but we expect that this study will encourage further research in this field, taking us one step closer to the ambitious goal of designing materials with distinct physical properties.

Acknowledgements

The authors thank P. Bristowe, S. Henke, M. Wharmby and W. Li for stimulating discussions. GK is the holder of a postdoctoral fellowship granted by the Deutsche Forschungsgemeinschaft (www.dfg.de/en/), KI1879. SS is supported by Cambridge Overseas Trust and AKC wishes to thank the European Research Council for an Advanced Investigator Award.

Notes and references

^a Department of Materials Science and Metallurgy, University of Cambridge, 27 Charles Babbage Road, Cambridge CB3 0FS, UK

† Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/

- 1 L. Tejuca and J. Fierro, *Properties and Applications of Perovskite-Type Oxides*, CRC Press, New York, 1993.
- 2 H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444.
- 3 A. K. Cheetham, C. N. R. Rao and R. K. Feller, *Chem. Commun*, 2006, 4780.
- 4 R. E. Morris and P. S. Wheatley, *Angew. Chem. Int. Ed*, 2008, **47**, 4966–4981.
- 5 L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. van Duyne and J. T. Hupp, *Chem. Rev*, 2012, **112**, 1105–1125.
- 6 P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev*, 2012, **112**, 1232–1268.
- 7 A. U. Czaja, N. Trukhan and U. Müller, *Chem. Soc. Rev*, 2009, **38**, 1284.
- 8 A. K. Cheetham and C. N. R. Rao, *Science*, 2007, **318**, 58–59.
- 9 P. Jain, N. S. Dalal, B. H. Toby, H. W. Kroto and A. K. Cheetham, *J. Am. Chem. Soc*, 2008, **130**, 10450–10451.
- 10 P. Jain, V. Ramachandran, R. J. Clark, H. D. Zhou, B. H. Toby, N. S. Dalal, H. W. Kroto and A. K. Cheetham, *J. Am. Chem. Soc*, 2009, **131**, 13625–13627.
- 11 D.-F. Wang, Z.-M. Wang and S. Gao, *Chem. Soc. Rev.*, 2011, **40**, 3157–3181.
- 12 D. B. Mitzi, C. A. Feild, W. T. A. Harrison and A. M. Guloy, *Nature*, 1994, **369**, 467–469.

- 13 J. Burschka, N. Pellet, S.-J. Moon, R. Humphry-Baker, P. Gao, M. K. Nazeeruddin and M. Grätzel, *Nature*, 2013, **499**, 316–319.
- 14 M. Liu, M. B. Johnston and H. J. Snaith, *Nature*, 2013, **501**, 395–398.
- 15 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
- 16 http://www.nrel.gov/ncpv/images/efficiency_chart.jpg, *National Renewable Energy Laboratory (NREL) 2013*.
- 17 D. Liu and T. L. Kelly, *Nat. Photon.*, 2014, **8**, 133–138.
- 18 D. B. Mitzi, *J. Chem. Soc., Dalton Trans.*, 2001, 1–12.
- 19 Z. Wang, K. Hu, S. Gao, H. Kobayashi, *Adv. Mater.*, 2010, **22**, 1526–1533.
- 20 V. M. Goldschmidt, *Naturwissenschaften*, 1926, **14**, 477–485.
- 21 A. M. Glazer, *Acta Crystallogr B Struct Crystallogr Cryst Chem*, 1972, **28**, 3384–3392.
- 22 A. F. Kapustinskii and Y. B. Yatsimirskii, *Zhurnal Obshchei Khimii*, 1949, **19**, 2191–2200.
- 23 R. D. Shannon, *Acta Cryst A*, 1976, **32**, 751–767.
- 24 W. Zhang, Y. Cai, R.-G. Xiong, H. Yoshikawa and K. Awaga, *Angew. Chem.Int. Ed.* 2010, **49**, 6608–6610.
- 25 F. A. Mautner, R. Cortés, L. Lezama and T. Rojo, *Angew. Chem. Int. Ed. Engl.*, 1996, **35**, 78–80.
- 26 X.-H. Zhao, X.-C. Huang, S.-L. Zhang, D. Shao, H.-Y. Wei and X.-Y. Wang *J. Am. Chem. Soc.*, 2013, **135**, 16006–16009.
- 27 B. Liu, R. Shang, K.-L. Hu, Z.-M. Wang and S. Gao, *Inorg. Chem.*, 2012, **51**, 13363–13372.
- 28 S. Chen, R. Shang, K.-L. Hu, Z.-M. Wang and S. Gao, *Inorg. Chem. Front.*, 2014, **1**, 83.
- 29 B. B. van Aken, T. T. Palstra, A. Filippetti and N. A. Spaldin, *Nat Mater*, 2004, **3**, 164–170.
- 30 I. Swainson, L. Chi, J.-H. Her, L. Crynswick, P. Stephens, B. Winkler, D. J. Wilson and V. Milman, *Acta Cryst.* 2010, **B66**, 422–429.
- 31 M. Mączka, A. Ciupa, A. Gągor, A. Sieradzki, A. Pikul, B. Macalik and M. Drozd, *Inorg. Chem.*, 2014, 140430123601002.