


 Cite this: *Nanoscale*, 2024, **16**, 9516

In situ growth of binder-free CoNi_{0.5}-MOF/CC electrode for high-performance flexible solid-state supercapacitor application†

 Weijie Zhang,^{‡a,b} Zhen Cao,^{‡b} Yuying Li,^b Ruiting Li,^b Yanmei Zheng,^c Ping Su^a and Xinli Guo *^b

Metal organic frameworks (MOFs) with binder-free electrodes have shown promise for portable electrochemical energy storage applications. However, their low specific capacitance and challenges associated with the attachment of active materials to the substrate constrain their practical utility. In this research, we prepared a CoNi_{0.5}-MOF/CC electrode by *in situ* growth of CoNi_{0.5}-MOF on an H₂O₂-pretreated carbon cloth (CC) without using any binder. It exhibits a higher specific capacitance of 1337.5 F g⁻¹ than that of CoNi_{0.5}-MOF (~578 F g⁻¹) at a current density of 1 A g⁻¹ and an excellent rate ability of 88% specific capacitance retention at a current density of 10 A g⁻¹ after 6000 cycles. The as-assembled flexible asymmetric solid-state supercapacitor based on the CoNi_{0.5}-MOF/CC positive electrode and a nitrogen-doped graphene (N-Gr) negative electrode exhibits an energy density of 61.46 W h kg⁻¹ at a power density of 1244.56 W kg⁻¹ and holds a stable capacitance of ~125 F g⁻¹ at 1 A g⁻¹ when the flexible supercapacitor is bent, showing great potential for flexible electronics application. The H₂O₂ is indicated to play an important role, enhancing the adhesion of CoNi_{0.5}-MOF on CC and reducing its charge transfer resistance by functionalizing the carbon fiber during the pretreatment of the CC matrix. The results provide a great way to prepare a flexible asymmetric solid-state supercapacitor with both high power density and high energy density for practical application.

Received 6th December 2023,

Accepted 8th April 2024

DOI: 10.1039/d3nr06225b

rsc.li/nanoscale

Introduction

Portable and wearable energy storage devices are attracting more interest with the demand for smartphones, electronic skin, and other intelligent devices. Flexible energy storage devices with high-performance electrochemical characteristics and good mechanical properties are becoming more and more important.^{1–3} Flexible all-solid-state supercapacitors provide fast charging and discharging processes, excellent power density and high cycle stability, which are ideal for powering portable devices. As part of a flexible device, the importance of a flexible electrode with superior mechanical properties, high

conductivity, and low resistance of the electrode active materials in a flexible supercapacitor cannot be overstated.

In the realm of supercapacitors, electrode materials hold paramount significance, with ongoing efforts directed towards the development of novel materials such as graphene, MXene, metal-organic frameworks (MOFs), and others, aimed at enhancing device performance. MOF materials, which are among the novel materials, consist of metal clusters and ligands. Previous research has shown that supercapacitors can take advantage of this material directly as an electrode material.^{4–6} Among them, the contact between the electrode and electrolyte can be facilitated by a porous structure in the material, thereby creating a double electric layer effect, and metal ions can undergo certain redox reactions with the electrolyte, resulting in pseudo-capacitance.^{7,8} In the previous works, Ni-MOF,^{9,10} Co-MOF,^{11,12} Fe-MOF,¹³ and Ni/Co-MOF,^{14,15} among others, showed great potential as supercapacitor electrode materials. Among them, the bimetal Ni/Co-MOF has a higher capacitance and more promising performance than the single MOF due to its high electrochemical activity. We also prepared Co/Ni-MOF powder material and studied the molar ratio of Co and Ni for their effects on electrochemical performance.¹⁶ The prepared CoNi_{0.5}-MOF

^aChongqing Key Laboratory of New Energy Storage Materials and Devices, School of Science, Chongqing University of Technology, Chongqing 40054, China

^bSchool of Materials Science and Engineer, Southeast University, Nanjing 211189, China. E-mail: guo.xinli@seu.edu.cn

^cJiangsu Co-Innovation Center of Efficient Processing and Utilization of Forest Resources, International Innovation Center for Forest Chemicals and Materials, College of Chemical Engineering, Nanjing Forestry University, Longpan Road 159, Nanjing 210037, China

†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3nr06225b>

‡The authors contributed equally to this work.



shows a relatively high capacitance of 578 F g^{-1} . However, there is still scope for improving its capacity properties. To improve the performance, using a binder-free electrode is effective, since the electrochemical properties of powder electrode materials are hindered by the binder material, which decreases the electron storage capacity and the transfer of ions. Thus, it is preferable to directly grow the active material without a binder on the collector substrate to avoid the binder as well as improve the electrochemical performance.^{17–19}

CC (carbon cloth) is considered as an appropriate substrate for flexible electrodes due to its flexibility and electrical conductivity. Furthermore, because of its wearability, intrinsic flexibility in mechanics, light weight and ease of integration with other materials, CC-based flexible devices have great potential for commercial use in practical applications. However, bare CC, when used as a MOF-based electrode matrix, exhibits unsatisfying performance in terms of inferior conductivity and electrochemical activity. To address the issues of bare CC, some strategies for improving CC performance have been presented, such as wet chemical oxidation, electrochemical oxidation, plasma modification *etc.*

Xu and co-workers prepared directly grown CoNi-MOF on CC with the hierarchical layered structure of ultrathin nanosheets and nanotube arrays, showing a high area capacity of 1.01 C cm^{-2} at 2 mA cm^{-2} .²⁰ To improve the hydrophilic and oxygen-containing functional groups on the CC, Ma and co-workers pretreated the CC with UV-ozone for 15 min, and then directly grew ZIF-67 on it. As a result, the maximum specific area capacitance of this hybrid electrode in 2 M KOH aqueous solution is 1756 mF cm^{-2} .²¹ Liu prepared manganese-based MOF on the surface of CC using a facile hydrothermal method. During the electrode preparation process, the commercially available original CC was ultrasonically rinsed for 30 min using 3 M HCl , absolute ethanol, and deionized water to increase the oxygen functional groups on the surface of the CC.²² To develop a high-performance MOF electrode, Wallace and co-workers pretreated the commercial CC and activated it in $\text{H}_2\text{SO}_4/\text{HNO}_3$ mixture at $70 \text{ }^\circ\text{C}$ for 3 hours, then by electrodeposition process, they successfully prepared the Co-MOF on pretreated CC, and the electrode showed superior capacitive performance.²³ However, to date, most carbon fibers or CC need to be treated with nitric acid or other strong corrosive fluids before their use as an electrode substrate, resulting in high energy demand and environmental contamination. Furthermore, natural and synthetic fabrics are typically passive in terms of electronic transmission, and the binding force between the load material and the textile is rather modest, as the physical contact interface is typically facilitated by van der Waals forces. As a result, the active material may fall off or be lost during the electrochemical reaction or mechanical deformation. Furthermore, the area capacitance generated by the electrode faces difficulty meeting the criteria due to the limited amount of active material in the load. Therefore, it is preferable to develop highly hydrophilic CC or textile with plentiful oxygen functional groups, and to enhance the pre-

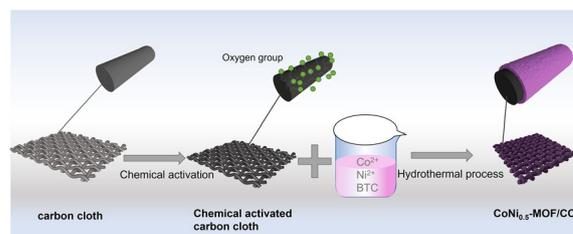


Fig. 1 Schematic illustration of the *in situ* growth process of $\text{CoNi}_{0.5}$ -MOF on CC.

treatment process to maximize the active material loading and specific capacitance of flexible electrode materials.^{24,25}

In this study, aimed at enhancing the performance of MOF material on a carbon cloth (CC) substrate, we present a straightforward pretreatment method for bare CC utilizing hydrogen peroxide, thereby avoiding the use of highly corrosive acids (Fig. 1). The resultant $\text{CoNi}_{0.5}$ -MOF, grown *in situ* on the pretreated CC ($\text{CoNi}_{0.5}$ -MOF/CC), exhibits outstanding capacitive properties, indicating promising potential for applications in flexible electronics.

Experimental

In situ growth of $\text{CoNi}_{0.5}$ -MOF on CC

The commercial CC was pretreated to modify the oxygen functional groups and surface hydrophilic properties. KOH , H_2O_2 and a mixture of HNO_3 , H_2SO_4 and KMnO_4 were used to pretreat the CC, respectively. The chemical processes were as follows: (1) CC was immersed into 2 M KOH solution and kept at $80 \text{ }^\circ\text{C}$ for 6 hours; (2) a few pieces of CC were dropped into $30\% \text{ H}_2\text{O}_2$ and kept at $50 \text{ }^\circ\text{C}$ for 6 hours; (3) some pieces of CC were modified with a mixture of concentrated HNO_3 , H_2SO_4 and KMnO_4 ($\text{HNO}_3/\text{H}_2\text{SO}_4/\text{KMnO}_4$ mixture). When the reaction finished, the CC was cleaned with deionized water and ethanol several times and dried under vacuum in an oven.

According to our previous report,¹⁶ the precursor solution of $\text{CoNi}_{0.5}$ -MOF was prepared. Subsequently, the pretreated carbon cloth was soaked in a $\text{Co}(\text{NO}_3)_2$ and $\text{Ni}(\text{NO}_3)_2$ solution, which included Co and Ni in a $1 : 0.5$ ratio, then 1,3,5-benzenetricarboxylic acid (H_3BTC) was added dropwise to the above beaker. After stirring for 30 min, the mixture was moved to the autoclave and reacted at $160 \text{ }^\circ\text{C}$ for 6 hours. When the reaction finished and the temperature decreased to ambient temperature, the $\text{CoNi}_{0.5}$ -MOF/CC was obtained after several washes with deionized water and ethanol, and the electrode was placed in a vacuum oven to dry overnight.

Characterization

In this work, the hydrophobicity of pretreated CC was tested by an optical contact angle measurement device (LAUDA Scientific, OSA100) using a droplet ($3 \mu\text{L}$) of water as an indicator at room temperature. Infrared spectrometry (FT-IR,



Thermo Fisher Scientific, Nicolet 5700) was used to characterize the oxygen group induced by the different chemical modifications. X-ray diffractometry (XRD, Bruker, D8-Discover, $\lambda = 1.5418 \text{ \AA}$) with Cu K α radiation was conducted to analyze the structure of the prepared material at the range of 10–80°. The morphology and chemical composition of the samples were characterized by scanning electron microscopy (SEM, Thermo Fisher Scientific, Sirion) and determined by energy dispersive spectroscopy (EDS), respectively.

Electrochemical test

An electrochemical workstation (CHI 660D) with a three-electrode system was used to evaluate the electrochemical performance of the electrode materials. Typically, 2 M KOH was used as the electrolyte. The counter electrode and reference electrode were platinum wire and Hg/HgO, respectively. For cyclic voltammetry (CV), the voltage window ranged from 0 to 0.6 V and the scan rate ranged from 1 to 50 mV s⁻¹. In order to test the capability of the prepared electrode materials, the galvanostatic charging/discharging (GCD) test was applied. The GCD test potential window was 0–0.6 V at current densities ranging from 1 to 30 A g⁻¹. The cycle stability was tested using GCD method, with 6000 cycles and a test current density of 10 A g⁻¹. For the electrochemical impedance spectra (EIS), the open-circuit voltage was set as the initial voltage, amplitude was 5 mV, and the frequency range was 0.01 Hz–100 kHz. In three-electrode test systems, the specific capacitance of the electrode material was measured by the following eqn (1):

$$C_s = \frac{I \times \Delta t}{m \times \Delta V} \quad (1)$$

where I , ΔV , m , Δt represent the discharge current density, working electrode voltage window, active material mass and discharge time, respectively. The electrochemical properties of the asymmetric supercapacitor device under study were tested by the two-electrode test system. Quasi-solid PVA/KOH gel was used as electrolyte and separator, CoNi_{0.5}-MOF/CC as cathode material, and N-rGO as anode material to assemble the asymmetric supercapacitor. The CV test had a voltage window of 0–1.7 V and a scan rate of 5–100 mV s⁻¹. The GCD was tested with a voltage window of 0–1.7 V and a current density of 1–10 A g⁻¹. The assembled asymmetric device's mass energy density and power density values were calculated from eqn (2) and (3) below:²⁶

$$E = \frac{C \times \Delta V^2}{2} \quad (2)$$

$$P = \frac{E \times 3600}{\Delta t} \quad (3)$$

where C , t , and ΔV are the specific capacitance at various current densities, the device discharge time and the potential window of the working device, respectively.

Results and discussion

The hydrophilicity of the substrate is very important, as it affects the *in situ* growth process of the active material. Hydrophilicity tests were performed to determine the optimal carbon fabric treatment for electrode material preparation. As shown in Fig. 2(a), the hydrophilicity test showed that the untreated carbon fiber has a higher contact angle and stronger hydrophobicity. The contact angles of the modified carbon fabrics with KOH decreased, but remained hydrophobic (Fig. 2b). In contrast, the HNO₃/H₂SO₄/KMnO₄ mixture-treated carbon cloth and the H₂O₂-treated carbon cloth are more hydrophilic (Fig. 2c and d), ensuring the active material grew uniformly on the carbon fabric during the hydrothermal process. Compared to treatment with HNO₃/H₂SO₄/KMnO₄ mixture, the same hydrophilic effect can be achieved with H₂O₂ pretreatment, which is not only more environmentally friendly but also a simpler process. Therefore, this experiment demonstrates that H₂O₂-pretreated CC can serve as an ideal *in situ* growth substrate for active electrode materials. The specific surface structure and functional groups were analyzed by the following FT-IR characterization.

The CCs were treated using different methods and examined by infrared spectroscopy to determine the functional groups on the surface. As depicted in Fig. 3(a), the infrared spectrum of the unhydroxylated original CC exhibits no discernible peaks corresponding to oxygen-related functional groups. In comparison, the H₂O₂ and HNO₃/H₂SO₄/KMnO₄ mixture added typical hydroxyl and other oxygen-containing functional groups to CC. The result indicates that H₂O₂ and the HNO₃/H₂SO₄/KMnO₄ mixture can significantly modify the surface structure of the carbon fabric. Specifically, the H₂O₂ and HNO₃/H₂SO₄/KMnO₄ mixture-modified CCs exhibit the absorption peak of –OH at about 3440 cm⁻¹–3650 cm⁻¹ and the stretching vibration peak of –C–H at about 1560 cm⁻¹.^{20,27} In addition, for the CC pretreated with H₂O₂, the characteristic peak of –C=O appeared at approximately 2250 cm⁻¹. The above oxygen groups are responsible for the hydrophilic properties. For comparison, we also used KOH as a modification agent and pretreated the CC for 6 h. As shown in Fig. 3(a), it is evident that despite the high alkalinity of KOH, the surface

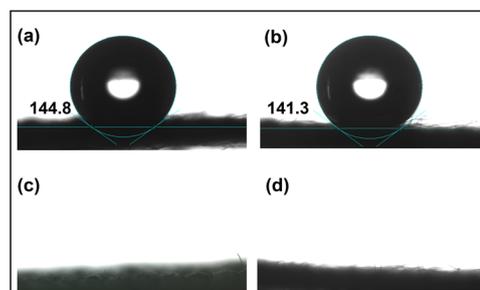


Fig. 2 Hydrophilicity test of CC after different pretreatment processes: (a) original CC; (b) treated with KOH; (c) treated with HNO₃/H₂SO₄/KMnO₄ mixture; (d) treated with H₂O₂.



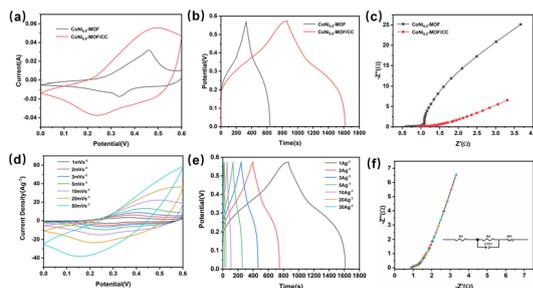


Fig. 6 Comparison of the electrochemical properties of CoNi_{0.5}-MOF and CoNi_{0.5}-MOF/CC: (a) CV curves at 20 mV s⁻¹; (b) GCD curves at 1 A g⁻¹; (c) EIS spectrum. Specific electrochemical properties of CoNi_{0.5}-MOF/CC; (d) CV curves at different scan rates; (e) GCD curves at different current densities; (f) EIS spectrum.

them, CoNi_{0.5}-MOF has the most advanced capacitance storage. Charge and discharge properties of CoNi_{0.5}-MOF/CC and CoNi_{0.5}-MOF were measured by galvanostatic charge and discharge test. Fig. 6(b) shows that the different electrode materials all have specific charging/discharging platforms, and the voltage locations of the platforms are comparable and consistent with the CV results, indicating that redox reactions of reactive substances occur in the same way. During charging and discharging, the redox reactions of Ni²⁺ and Ni³⁺ as well as Co²⁺ and Co³⁺ ions are responsible for the high specific capacitance and the charge–discharge curve plateau. According to the GCD curve test results, the specific capacitance of CoNi_{0.5}-MOF/CC at 1 A g⁻¹ current density is 1337.5 F g⁻¹, while the specific capacitance of CoNi_{0.5}-MOF is 578 F g⁻¹. The results reveal that *in situ* developed CoNi_{0.5}-MOF material on CC has improved electrochemical performance.

The electrode reaction's kinetic process can be effectively reflected by EIS. Fig. 6(c) shows the EIS spectrum of the electrode material in the frequency range of 0.01 Hz–100 kHz under voltage disturbance with amplitude of 5 mV. The electrode resistance and charge transfer resistance are in the high-frequency region, and the Warburg impedance formed by electrolyte diffusion in the electrode is in the low-frequency area.²⁹ Due to the addition of a conductive substance, the powder electrode has a smaller R_s (0.54 Ω) than the CoNi_{0.5}-MOF/CC. However, CoNi_{0.5}-MOF/CC has a decreased charge transfer resistance because electrolyte ions may easily diffuse to the reactive site of the electrode material without conductive agents and binders. Furthermore, the as-prepared CoNi_{0.5}-MOF/CC electrode material has a lower Warburg impedance, indicating that the *in situ* grown material has sufficient contact with the electrolyte and superior electrochemical performance.

To further investigate the electrochemical performance of CoNi_{0.5}-MOF/CC, Fig. 6(d) shows the CV curves of CoNi_{0.5}-MOF/CC electrodes at various scan rates. The electrode displays a strong redox peak at a low scan rate. Ions can be absorbed to the surface and inside of the material at slow scan rates, resulting in a typical redox reaction. However, the redox peak weakens with increasing scan rate because surface

adsorption is the predominant electrochemical process at high sweep speed, and there is some electrochemical polarization, thus the redox peak has a certain divergence.^{30,31} GCD tests were conducted to assess the rate performance of the CoNi_{0.5}-MOF/CC electrode at different current densities. Fig. 6(e) shows that when current density increases, the electrode exhibits a fast charge/discharge ability and good reversibility. The discharge time of the electrode is 749 seconds when the current density is 1 A g⁻¹. The fully charged electrode can be released in only 13 seconds when the current density is 30 A g⁻¹, demonstrating remarkable high-power charge–discharge performance. Fig. 6(f) shows the EIS spectrum of CoNi_{0.5}-MOF/CC and the inserted equivalent resistance fitted by Zview software. The result shows that the prepared electrodes have very low charge transfer resistance (0.38 Ω), allowing the electrolyte ion to effectively diffuse into the active site.

Electrode rate performance and cycle stability are important for practical application. Fig. 7(a) shows that the specific capacitance values of the CoNi_{0.5}-MOF/CC electrode are 1337.5 F g⁻¹, 1267.5 F g⁻¹, 1205.3 F g⁻¹, 1146.8 F g⁻¹, 1040.8 F g⁻¹, 961.5 F g⁻¹, and 872.6 F g⁻¹ at the current densities of 1 A g⁻¹, 2 A g⁻¹, 3 A g⁻¹, 5 A g⁻¹, 10 A g⁻¹, 20 A g⁻¹ and 30 A g⁻¹, respectively. Even with a 30 A g⁻¹ current density, the electrode can still reach 872.6 F g⁻¹, indicating good rate performance. Furthermore, the electrode was tested for cycling performance over 6000 charge/discharge cycles at 10 A g⁻¹, as shown in Fig. 7(b). The result shows that the material keeps 88% of its original capacity after cycling tests, showing remarkable cycle stability. Fig. S2 and S3† verified that the excellent rate performance and cycling stability of the material are attributable to the chemical binding of the active material with the CC substrate, and the material's stable nanostructure provides buffer space for expansion during the charging/discharging process.

We utilized the analysis method given by Dunn³² and Trassatti³³ to investigate the charge storage dynamics of the CoNi_{0.5}-MOF/CC electrode. The overall capacity stored in the electrode material can be categorized into the capacitance produced by diffusion and surface reaction processes using Dunn's kinetic method. In detail, the capacitance of the material at different scanning rates during CV testing is analyzed by following eqn (4):

$$i = av^b \quad (4)$$

where i is the peak current (A) of the CV curve, v is the scan rate (V s⁻¹), and the slope b can be calculated from the log(i)

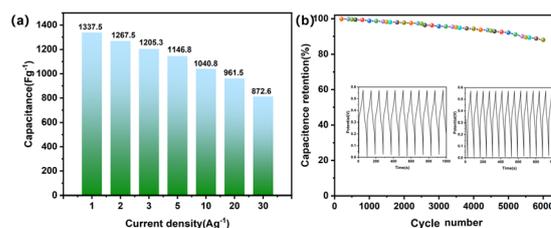


Fig. 7 (a) Rate performance; (b) cycling performance of CoNi_{0.5}-MOF/CC.



vs. $\log(\nu)$. Here, $b = 0.5$ represents the diffusion control process, while $b = 1$ represents the surface capacitance process. As shown in Fig. 8(a), the anode and cathode values are $b = 0.84458$ and $b = 0.70279$, respectively, showing that the surface process dominates capacitance. Fig. 8(b) shows the change in the capacitance's contribution to charge storage at different scanning rates. As shown in Fig. 8(b), the electrochemical reaction is dominated by ion diffusion and redox reaction at a low scan rate. The surface reaction becomes more dominant in the electrochemical reaction, and the capacitance contribution eventually increases.

The contribution of surface processing capacitance to the total charge is further investigated at different scan rates, and Dunn's method was applied to fit and analyse the CV curves. The results show that at low scan rates, the capacitance contribution is minimal. At low scan rates, the electrolyte ions have enough time to penetrate into the electrode material, resulting in less surface capacitive behaviour. With the scan rate increase, the redox reaction occurs too late, and the capacitance primarily comes from the surface reaction process, so the capacitance of the surface process has a certain increase to the total amount of capacitance, and the surface process occupies the main process of the entire electrode reaction.

The total charge stored in the electrode can be separated into three parts using Trasatti's kinetic research method: (1) Faraday charge generated by the slow diffusion of ions during the ion insertion process; (2) Faraday charge generated by rapid surface charge transfer or pseudo-capacitance; (3) double layer capacitive charge generated by non-Faraday process. The first is used for diffused charge storage, while the last two are utilized for capacitive charge storage. The theoretical stored charge in Trasatti's method is represented by the following equation:

$$Q(\nu) = Q(c) + a\nu^{-\frac{1}{2}} \quad (5)$$

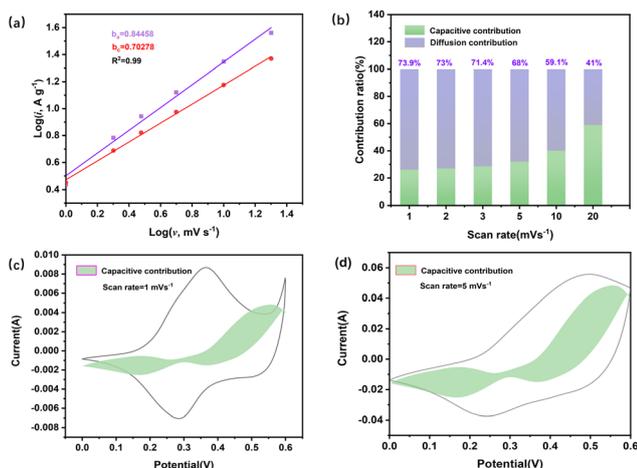


Fig. 8 (a) Kinetic characteristics and reaction mechanism of CoNi_{0.5}-MOF/CC electrode; (b) the capacitive contribution of CoNi_{0.5}-MOF/CC at different scan rates; (c and d) the capacitive contribution at 1 mV s⁻¹ and 5 mV s⁻¹.

$$\frac{1}{Q(c)} = \frac{1}{Q(t)} + a\nu^{\frac{1}{2}}, \quad (6)$$

where $Q(\nu)$ is the total charge measured, $Q(c)$ represents the capacitive charge (including the double layer and the pseudo-capacitance process), $Q(t)$ is the theoretical total stored charge, a is a constant, and ν is the scanning rate. When ν approaches infinity, the diffused charge in eqn (5) can be ignored, and the $Q(c)$ of the theoretical capacitive charge can be calculated from the intercept in the graph of $Q(\nu)$ and $\nu^{\frac{1}{2}}$. When ν is close to zero in eqn (6), the time is sufficiently long to permit ions to reach all locations in the electrode material, and the theoretical faradaic charge can be computed by extending the linear relationship between $\frac{1}{Q(\nu)}$ and $\nu^{\frac{1}{2}}$. The difference between $Q(t)$ and $Q(c)$ yields the diffused charge storage value $Q(d)$. As shown in Fig. 9(a and b), $Q(t)$ of the electrode at low sweep speed is 1303 C g⁻¹, while the capacitance stored charge is 570.386 C g⁻¹.

Taking CoNi_{0.5}-MOF/CC as the positive electrode, an asymmetric flexible supercapacitor was assembled, with N-doped graphene (N-Gr) as the negative electrode and KOH/PVA as the gel electrolyte to test the practical application performance of the no-binder CoNi_{0.5}-MOF/CC electrode, as shown in Fig. 10(a). The electrochemical performance was examined by CV, GCD, and EIS in a two-electrode system. Fig. 10(b) shows the CV curves of the asymmetric supercapacitor at different scanning rates. The results show that the capacitor's voltage can reach 1.7 V, which is sufficient to power a number of smart electronic devices. In addition, although the general shape of the CV curves is nearly rectangular during this potential window, there are redox peaks at various scanning rates. It demonstrated that the coexistence of double layer capacitance and pseudo-capacitance is the operating mechanism of the supercapacitor. The device's charge-discharge capability was tested using GCD method at various current densities. Fig. 10 exhibits that the device obtained the specific capacitance of 160.6 F g⁻¹, 156.2 F g⁻¹, 151.2 F g⁻¹, 146.6 F g⁻¹ and 102.5 F g⁻¹ at current densities of 1 A g⁻¹, 2 A g⁻¹, 3 A g⁻¹, 5 A g⁻¹, and 10 A g⁻¹ respectively. As the current density increases, the capacitance decreases slightly as the resistance of the capacitor increases and the internal potential increases, leading to an increase in IR drop. In comparison with other devices, however, the assembled device exhibits exceptional rate per-

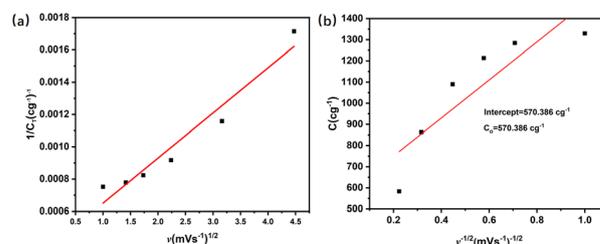


Fig. 9 Kinetic characteristics and reaction mechanism of CoNi_{0.5}-MOF/CC electrode: (a) fitting theoretical capacity; (b) fitting theoretical capacitive capacity (Trasatti's method).



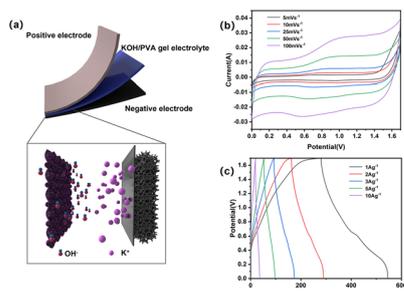


Fig. 10 (a) Schematic illustration of flexible asymmetric capacitor; (b) CV curves; (c) GCD curves.

formance, indicating that the supercapacitor can be charged and discharged effectively at high current density.

To assess its flexibility, the device underwent bending ranging from 90 to 180 degrees followed by a charge–discharge test to evaluate its performance under bending conditions. Fig. 11(a and b) shows photos of the device, flat and bent. Fig. 11(c and d) compares the GCD curves and EIS impedance spectra measured under bending conditions. Although the voltage does not reach 1.7 V because the contact between electrodes is not as excellent as it is under flat conditions, the device has a high charge–discharge capacity of 125 F g⁻¹ under bending conditions at 1 A g⁻¹ current density, which is a little less than that of the unbent device. The EIS spectrum indicates that the decreased capacitance may be attributed to the R_s and Warburg impedance of the electrode material increasing after bending.

The electrochemical impedance spectrum of the assembled asymmetric supercapacitor device was fitted to further analyze its dynamic characteristics. As depicted in Fig. 12(a), impedance data can be obtained from fitted equivalent circuit models. Table 1 summarizes the corresponding parameter values of the circuit components. The solution resistance (R_s), charge transfer resistance (R_{ct}), double layer capacitance (CPE) and Warburg diffusion resistance comprise the circuit model.

According to the analog equivalent circuit, the device has a small R_s (3.121Ω). W–P is the Warburg diffusion coefficient, and when it is 0.5, it indicates capacitive diffusion. The value obtained after fitting is 0.6825, showing a combination of

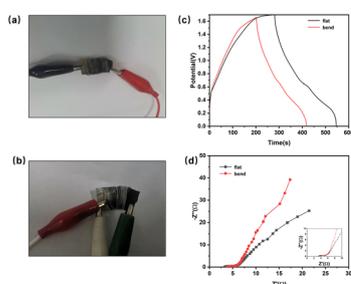


Fig. 11 (a and b) Photos of assembled supercapacitor in flat and bent state; (c) GCD performance comparison before and after bending; (d) EIS spectrum.

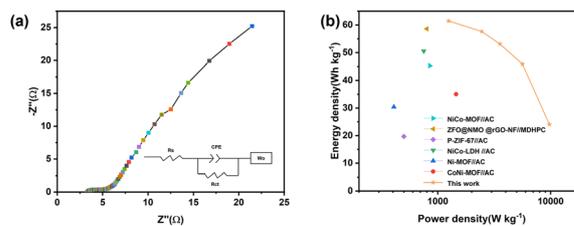


Fig. 12 CoNi_{0.5}-MOF/CC//N-Gr asymmetric capacitor: (a) EIS plot; (b) Ragone plot.

Table 1 CoNi_{0.5}-MOF/CC//N-Gr asymmetric supercapacitor EIS fitting data

Device	R_s	CPE-P	R_{ct}	W–P	W–R
CoNi _{0.5} -MOF/CC//N-Gr	3.121 Ω	0.4323 Ω	2.375 Ω	0.6825	85.78 Ω

pseudo-capacitance and double layer capacitance, which is consistent with the asymmetric device structure.

For practical applications, energy density and power density are critical. According to eqn (2) and (3), the CoNi_{0.5}-MOF/CC//N-Gr asymmetric supercapacitor has an energy density of 61.46 W h kg⁻¹ at the power density of 1244.56 W kg⁻¹. The device obtained various energy densities at different power densities, such as 57.64 W h kg⁻¹ at 2444.4 W kg⁻¹, 53.1 W h kg⁻¹ at 3555.1 W kg⁻¹, and 45.83 W h kg⁻¹ at 5625 W kg⁻¹, and even at a high-power density of 9747 W kg⁻¹, it still has an energy density of 24.0667 W h kg⁻¹, showing good rate performance and excellent energy storage characteristics. The Ragone plot in Fig. 12(b) and Table S1† show that this device has superior energy and power density when compared to the asymmetric capacitor devices assembled by other related materials.^{33–39} The assembled device with high practical energy density and power density shows promising application prospects.

Conclusions

In summary, we have developed a binder-free CoNi_{0.5}-MOF/CC electrode with excellent capacitive properties by *in situ* growth of CoNi_{0.5}-MOF on CC pretreated with H₂O₂. This electrode exhibits a notably higher specific capacitance of 1337.5 F g⁻¹ compared to CoNi_{0.5}-MOF (~578 F g⁻¹) at a current density of 1 A g⁻¹, alongside an excellent rate capability of 88% specific capacitance retention at a current density of 10 A g⁻¹ after 6000 cycles. Moreover, the flexible asymmetric solid-state supercapacitor assembled with CoNi_{0.5}-MOF/CC was used as the positive electrode with nitrogen-doped graphene (N-Gr) as the negative electrode, achieving an energy density of 61.46 W h kg⁻¹ at a power density of 1244.56 W kg⁻¹. Remarkably, it maintains a stable capacitance of ~125 F g⁻¹ at 1 A g⁻¹ even when subjected to bending, showcasing its significant potential for application in flexible electronics.



Author contributions

Weijie Zhang contributed to the conception, design, analysis and writing of the study. Zhen Cao contributed to the design, analysis and writing of the study. Yuying Li contributed to the analysis of the study. Ruiting Li contributed to the analysis of the study. Yanmei Zheng contributed to the analysis of the study. Ping Su contributed to the writing of the study. Xinli Guo contributed to the design, analysis, and writing of the study and provided the funding support.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to thank the financial support from the National Natural Science Foundation of China (51574054), the Scientific Research Foundation of Chongqing University of Technology (0101220631), Chongqing Municipal Education Commission (KJZD-K202201107, KJQN202301102), Chongqing Science and Technology Bureau (CSTB2022NSCQ-MSX0356, 2023TIAD-KPX0126), Joint Fund of Chongqing Municipal Education Commission and Science and Technology Bureau (CSTB2022NSCQ-LZX0032) and Professional Experimental Center of Chongqing University of Technology.

References

- D. Fu, H. Li, X.-M. Zhang, G. Han, H. Zhou and Y. Chang, *Mater. Chem. Phys.*, 2016, **179**, 166–173.
- L. Han, H. Huang, X. Fu, J. Li, Z. Yang, X. Liu, L. Pan and M. Xu, *Chem. Eng. J.*, 2020, **392**, 123733.
- X. He, X. Mao, C. Zhang, W. Yang, Y. Zhou, Y. Yang and J. Xu, *J. Mater. Sci.: Mater. Electron.*, 2019, **31**, 2145–2152.
- D. P. Dubal, K. Jayaramulu, J. Sunil, Š. Kment, P. Gomez-Romero, C. Narayana, R. Zbořil and R. A. Fischer, *Adv. Funct. Mater.*, 2019, **29**, 1900532.
- B. Liu, H. Shioyama, H. Jiang, X. Zhang and Q. Xu, *Carbon*, 2010, **48**, 456–463.
- V. Shrivastav, S. Sundriyal, P. Goel, H. Kaur, S. K. Tuteja, K. Vikrant, K.-H. Kim, U. K. Tiwari and A. Deep, *Coord. Chem. Rev.*, 2019, **393**, 48–78.
- D. Ji, H. Zhou, Y. Tong, J. Wang, M. Zhu, T. Chen and A. Yuan, *Chem. Eng. J.*, 2017, **313**, 1623–1632.
- H. Jia, Z. Wang, X. Zheng, Y. Cai, J. Lin, H. Liang, J. Qi, J. Cao, J. Feng and W. Fei, *Electrochim. Acta*, 2019, **312**, 54–61.
- A. A. Bhoite, K. V. Patil, R. S. Redekar, P. S. Pati, V. A. Sawant and N. L. Tarwal, *J. Solid State Chem.*, 2023, **326**, 124192.
- Y. Xiao, W. Wei, M. Zhang, S. Jiao, Y. Shi and S. Ding, *ACS Appl. Energy Mater.*, 2019, **2**(3), 2169–2177.
- W. Xuan, R. Ramachandran, C. Zhao and F. Wan, *J. Solid State Electrochem.*, 2018, **22**, 3873–3881.
- H. Zhang, J. Wang, Y. Sun, X. Zhang, H. Yang and B. Lin, *J. Alloys Compd.*, 2021, **879**, 160423.
- B. Ramasubramanian, C. Chinglenthoba, X. Huiqing, N. Xiping, H. K. Hui, S. Valiyaveetil, S. Ramakrishna and V. Chellappan, *Surf. Interfaces*, 2022, **34**, 102397.
- F. Ren, Y. Ji, F. Chen, Y. Qian, J. Tian and J. Wang, *Mater. Chem. Front.*, 2021, **5**(19), 7333–7342.
- X. Hang, J. Zhao, Y. Xue, R. Yang and H. Pang, *J. Colloid Interface Sci.*, 2022, **628**, 389–396.
- W. Zhang, X. Guo, Y. Wang, Y. Zheng, J. Zhao, H. Xie, Z. Zhang and Y. Zhao, *Energy Fuels*, 2022, **36**, 1716–1725.
- H. S. Kim, M. S. Kang and W. C. Yoo, *J. Mater. Chem. A*, 2019, **7**, 5561–5574.
- G. Li, H. Cai, X. Li, J. Zhang, D. Zhang, Y. Yang and J. Xiong, *ACS Appl. Mater. Interfaces*, 2019, **11**, 37675–37684.
- S. Li, K. Yang, P. Ye, K. Ma, Z. Zhang and Q. Huang, *Appl. Surf. Sci.*, 2020, **503**, 144090.
- S. Xu, R. Liu, X. Shi, Y. Ma, M. Hong, X. Chen, T. Wang, F. Li, N. Hu and Z. Yang, *Electrochim. Acta*, 2020, **342**, 136124.
- J. Ma, J. Li, R. Guo, H. Xu, F. Shi, L. Dang, Z. Liu, J. Sun and Z. Lei, *J. Power Sources*, 2019, **428**, 124–130.
- Y. Liu, J. Liu, Y. Cao, W. Shang, N. Peng, X. Long, S. Zhou and Y. Wen, *J. Electrochem. Energy Convers. Storage*, 2022, **19**, 031002.
- Y. Han, J. Cui, Y. Yu, Y. Chao, D. Li, C. Wang and G. G. Wallace, *ChemSusChem*, 2022, **15**, 202200644.
- R. Hou, M. Miao, Q. Wang, T. Yue, H. Liu, H. S. Park, K. Qi and B. Y. Xia, *Adv. Energy Mater.*, 2019, **10**, 1901892.
- H. Huang, P. He, T. Huang, S. Hu, T. Xu, H. Gu, S. Yang, L. Song, X. Xie and G. Ding, *ACS Appl. Mater. Interfaces*, 2019, **11**, 1239–1246.
- W. Zhang, Z. Chen, X. Guo, K. Jin, Y. Wang, L. Li and T. Zhang, *Electrochim. Acta*, 2018, **278**, 51–60.
- Y. Zhao, H. Dong, X. He, J. Yu, R. Chen, Q. Liu, J. Liu, H. Zhang, J. Yu and J. Wang, *ChemElectroChem*, 2019, **6**, 3355–3366.
- M. Zhang, D. Hu, Z. Xu, B. Liu, M. Boubeche, Z. Chen, Y. Wang, H. Luo and K. Yan, *J. Mater. Sci. Technol.*, 2021, **72**, 172–179.
- Y. Yan, J. Lin, T. Xu, B. Liu, K. Huang, L. Qiao, S. D. Liu and J. Qi, *Adv. Energy Mater.*, 2022, **12**(24), 2200434.
- C. Guo, Y. Zhang, M. Yin, J. Shi, W. Zhang, X. Wang, Y. Wu, J. Ma, D. Yuan and C. Jia, *J. Power Sources*, 2021, **485**, 229315.
- F. He, K. Li, S. Cong, H. Yuan, X. Wang, B. Wu, R. Zhang, J. Chu, M. Gong, S. Xiong, Y. Wu and A. Zhou, *ACS Appl. Energy Mater.*, 2021, **4**, 7731–7742.
- J. Wang, J. Polleux, J. Lim and B. Dunn, *J. Phys. Chem. C*, 2007, **111**, 14925–14931.
- S. Ardizzone, G. Fregonara and S. Trasatti, *Electrochim. Acta*, 1990, **35**(1), 263–267.



- 34 X. Chu, F. Meng, W. Zhang, H. Yang, X. Zou, S. Molin, P. Jasinski, X. Sun and W. Zheng, *Nanotechnology*, 2022, **33**, 205403.
- 35 J. Wang, Y. Ma, X. Kang, H. Yang, B. Liu, S. Li, X. Zhang and F. Ran, *J. Solid State Chem.*, 2022, **309**, 122994.
- 36 W. Wang, Y. Fang, S. Wang, Z. Zhang, R. Zhao and W. Xue, *J. Alloys Compd.*, 2022, **900**, 163532.
- 37 Z. Ma, J. Li, R. Ma, J. He, X. Song, Y. Yu, Y. Quan and G. Wang, *New J. Chem.*, 2022, **46**, 7230–7241.
- 38 J. Acharya, B. Pant, G. P. Ojha and M. Park, *J. Colloid Interface Sci.*, 2022, **610**, 863–878.
- 39 H. Li, X. Wang, L. Dai, F. Guo, H. Mi, C. Ji and L. Sun, *Inorg. Chem.*, 2022, **61**, 3866–3874.

