

Environmental Science Nano

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: V. Alcolea-Rodriguez, R. Portela, V. Calvino-Casilda and M. Bañares, *Environ. Sci.: Nano*, 2024, DOI: 10.1039/D3EN00810J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Data availability statements

View Article Online
DOI: 10.1039/D3EN00810J

All data supporting the findings of this study are presented in the main article and in the Supplementary Information.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Open Access Article. Published on 09/08/2024. Downloaded on 09/08/2024. This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.





Victor Alcolea-Rodriguez
Instituto de Catálisis y Petroleoquímica,
CSIC, C/ Marie Curie, 2
28049 Madrid, Spain
View Article Online
DOI: 10.1039/D3EN00810J

Environmental Science: Nano

Environmental Significance Statement

Nanomaterials hazard is associated with their surface reactivity. We report an *in chemico* approach to probe the number, nature and reactivity of surface sites. This approach tells how many sites we have at the surface of nanomaterials; relevant for a dose metric based on actual sites rather than on surface or mass. This would allow better insight on dose-response investigations. This NAM provides insights into whether sites are oxidative, acidic, basic, or a combination thereof, and additionally aids in ranking NMs by reactivity, which is crucial for understanding their mechanisms of toxicity. In a broader view, it can characterize nanomaterials and how their reactivity evolves as they change making multicomponent nanomaterials and as they age during operation and in the environment.

Environmental Science: Nano Accepted Manuscript

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Open Access Article. Published on 09/08/2024. Downloaded on 11/02/2024 8:33:00 AM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

***In chemico* methodology for engineered nanomaterials categorization according to number, nature and oxidative potential of reactive surface sites**

V. Alcolea-Rodriguez^{a*}, R. Portela^a, V. Calvino-Casilda^b, M.A. Bañares^{a*}

^a Instituto de Catálisis y Petroleoquímica, ICP-CSIC, Marie Curie 2, 28049-Madrid, Spain

^b Departamento de Ingeniería Eléctrica, Electrónica, Control, Telemática y Química Aplicada a la Ingeniería, E.T.S. de Ingenieros Industriales, UNED, Juan del Rosal 12, 28040-Madrid, Spain

*Corresponding authors: miguel.banares@csic.es victor.alcolea@csic.es

Keywords

Surface descriptor, chemisorption, oxidative potential, active sites, dose metrics, probe molecule, probe reaction, new approach methodologies

Abstract

Methanol probe chemisorption quantifies the number of reactive sites at the surface of engineered nanomaterials, enabling normalization per reactive site in reactivity and toxicity tests, rather than per mass or physical surface area. Subsequent *temperature-programmed surface reaction* (TPSR) of chemisorbed methanol identifies the reactive nature of surface sites (acidic, basic, redox or combination thereof) and their reactivity. Complementary to methanol assay, dithiothreitol (DTT) probe oxidation reaction is used to evaluate oxidation capacity. These acellular approaches to quantify the number, nature, and reactivity of surface sites constitute a New Approach Methodology (NAM) for site-specific classification of nanomaterials. As a proof of concept, CuO, CeO₂, ZnO, Fe₃O₄, CuFe₂O₄, Co₃O₄ and two TiO₂ nanomaterials were probed, and a harmonized reactive descriptor was obtained: DTT oxidation rate per reactive site, or *Oxidative Turnover Frequency* (OxTOF). CuO and CuFe₂O₄ nanoparticles exhibit the largest reactive sites surface density and are the most oxidative in the series, as estimated by DTT probe reaction, followed by CeO₂ NM-211 and, then, by titania nanomaterials (DT-51 and NM-101) and Fe₃O₄. DTT depletion in ZnO NM-110 was associated with dissolved zinc ions rather than the ZnO particles themselves, but the basic character of the ZnO NM-110 particles surface was evidenced by methanol TPSR. These acellular assays allow ranking the 8 nanomaterials into three categories with statistically different oxidative potential: CuO, CuFe₂O₄ and Co₃O₄ are the most reactive, ceria exhibits a moderate reactivity, and iron oxide and the titanias possess a low oxidative potential.

1 INTRODUCTION

The surface of engineered nanomaterials (ENMs). Metal oxides possess a lattice which unit cell repeats *ad infinitum*. However, materials are finite, and interact with the surrounding environment through their surface, the end of the lattice periodic structure, which is characterized by descriptors such as specific surface area (BET area), pore size, or zeta-potential (ζ).¹ Surface chemistry defines materials' reactivity (type and strength), in metal oxides often associated with surface oxygen species, such as bridging oxygen, oxide, superoxide, peroxide, or hydroxyl sites (**Error! Reference source not found.**), which properties are determined by underlying cations, defects, and the bulk structure. Charge unbalances such as surface vacancies, defects and others, are stabilized to keep the material neutrality, typically by surface interactions with, e.g., environmental water, generating surface hydroxyl groups. The compensation mechanisms for defects may vary depending on the nature of the material; like the formation of *farb* centers, covalent bonding or transitions between valence and conduction bands in ionic, covalent on transition element oxides, respectively². Surface relevance is maximized in non-soluble nanomaterials (NMs, with one dimension in the 1-100 nm range)³, in which a high surface-to-volume ratio confers them with distinctive properties. For example, in the field of ecotoxicology, 40 mg/L of nano-sized CuO particles completely inhibit the growth of *S. cerevisiae*, while 4000 mg/L of CuO bulk material are needed⁴; the number of exposed sites is probably not dramatically different between these two very different amounts of CuO materials.

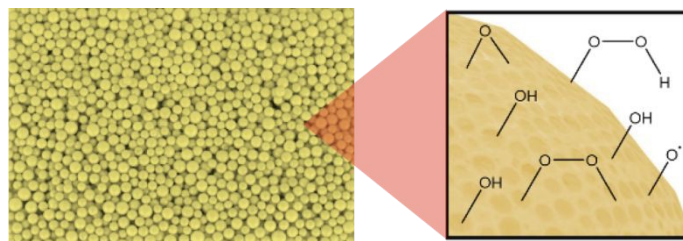


Figure 1. Reactive sites on ENMs surface

Rise of engineered nanomaterials and concern about their toxicity. Engineered nanomaterials applications have grown significantly, influencing societal challenges and the economy, especially in Asia-Pacific, America, and Europe.^{5,6,7} Transition metal oxide ENMs, including TiO₂, CuO, ZnO, and others, have versatile uses like pigments and catalysts.^{8,9} This has prompted numerous characterization, exposure and hazard studies¹⁰⁻¹² to understand and prevent possible adverse effects or pathologies, e.g. derived from reactive

 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



oxygen species (ROS) release,^{13,14} and to adopt a knowledge-based safe-by-design (SbD) approach^{15,16}, essential to ensure safe ENM applications as well as faster, economic and more effective production routes.^{17,18} Integrated information related to toxicity (*in vitro* and *in vivo* testing) and physicochemical properties underpins hazard prediction^{16, 19, 20, 21 22 23}, with machine learning serving as the primary tool.²⁴ Grouping ENMs based on similarities can optimize resource management, aligning with OCDE guidelines for risk assessment and promoting non-animal testing methodologies.^{25,26} New approach methodologies (NAMs) may provide the basis for this objective.^{27,28,29} The overarching aim is to contribute to the understanding of Adverse Outcome Pathways (AOPs) and, particularly, what reactive properties are associated with the triggering of adverse effects by nanomaterials.³⁰

New approach methodology based on surface sites reactivity. Nanomaterial surface reactivity plays a vital role in oxidative-stress-induced adverse effects.^{31,32,33,34} As reactivity is an extrinsic property considered a key parameter to describe the interaction of ENMs with their surroundings,^{16, 19} the development of abiotic *in chemico* assays to evaluate surface reactivity and link it with key events in reactive-based nanotoxicity would help to fundamentally understand the modes of action^{35,36,37} and better group ENMs while minimizing *in vivo* testing.³⁸ Surface reactivity characterization complements other physicochemical information relevant to the nanotoxicity field¹⁹ to investigate toxic ion release, lung fibrosis, inflammasome activation, interference with embryonic hatching or membrane lysis, among others. In the context of reactive-based toxicity assessment of engineered nanomaterials, it is widely acknowledged that materials with identical chemical compositions can lead to significantly varied biological oxidative damage.³⁴ Thus, characterizing the amount, nature and reactivity of surface sites is essential for identifying an additional parameter impacting nanomaterial's effects. The interaction with biological systems depends on the surface properties of the nanomaterials, the presence of any kind of active site may have effects on their interaction with molecules. We hypothesize that mapping all reactive sites (redox, acidic and basic) may provide a better reactive description of nanomaterials than just oxidative sites, and enable a more reliable grouping of nanomaterials based on their surface reactivity. Formally equivalent problems have formally equivalent solutions: as key events in reactive-based toxicity and catalytic reactions occur at the surface, more specifically, at the reactive sites, we propose the use of catalytic methods based on adsorption and reaction of probe molecules to quantify the surface

1
2
3 reactive sites of ENMs and to characterize their reactive nature, thus delivering descriptors
4 relevant for ENMs classification.^{39,40}
5
6

7
8 The reactive characterization may also provide new dose metrics. In *in vitro* tests with
9 different cell lines, quantitative dose-dependent cellular/biological effects are typically
10 normalized by mass or physical BET area. These dose metrics may sometimes not be useful
11 to compare exposure because mass or exposed physical area do not necessarily correlate
12 with the number of reactive sites, which trigger chemical processes, *e.g.*, ROS formation
13 (generation of ROS by particles is one of the possible molecular initiating events that lead
14 to adverse outcomes, as confirmed *e.g.* for PM, CuO, or photo-activated TiO₂). We do not
15 tackle photocatalytic phenomena that are unlikely to happen inside the body. Research in
16 heterogeneous catalysis has traditionally faced the same challenge when comparing the
17 activity of catalytic materials and has reached a consensus that the most relevant metric is
18 the turnover frequency (TOF). TOF is the number of times that the overall catalytic reaction
19 takes place (*i.e.*, molecules that react) per reactive site and unit time.^{41,39,42,43,44} Our research
20 posits that probe molecules will allow quantification of reactive surface sites, their nature
21 and reactivity; TOF calculation can thus be made based on relevant probe reactions (*e.g.*,
22 DTT), offering new metrics for reactivity and toxicological studies.
23
24

25
26 The most typical probe molecules used to quantify reactive sites in heterogeneous catalysis
27 are carbon monoxide, for metal NPs,⁴⁵ and methanol, for metal oxides, both in the gas/vapor
28 phase. The latter is considered a “smart” probe molecule that can not only quantify the
29 number of surface sites by chemisorption, but also report on their reactive profile by
30 temperature-programmed surface reaction (TPSR),^{46,47} a powerful technique to identify and
31 quantify acidic, basic, redox, and bifunctional sites^{48,49} on materials that are not thermally
32 sensitive. In addition, several probe molecules in the liquid phase may specifically assess
33 the oxidative potential (OP),^{50,51,52,53,54,55} which is particularly relevant to human health due
34 to its involvement in cellular damage by oxidative stress.^{10,56,57,58,59,60} Among those,
35 dithiothreitol (DTT) is suggested here as an acellular, liquid-phase, low-temperature probe
36 reaction to assess the nanomaterials OP, as this molecule has been previously used to
37 quantify the oxidative capacity of particulate matter.^{61,62,63,64,65,66} We introduce therefore a
38 NAM based on using gas-phase methanol chemisorption and subsequent TPSR as well as
39 liquid-phase DTT consumption in PBS-water solutions with nanomaterials. By normalizing
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

DTT oxidation rate via methanol chemisorption, we derive the Oxidative Turnover Frequency (OxTOF) to measure surface site reactivity. We suggest dose normalization to the reactive sites' amount and reactivity. As a proof of concept seven metal oxide nanomaterials (CeO_2 , ZnO , CuO , Fe_3O_4 , Co_3O_4 , and two TiO_2 variants), one bimetallic nanooxide (CuFe_2O_4) and an oxide with larger particles (Co_3O_4) are analyzed to investigate the usefulness of this NAM to 1), categorize the reactivity of eight benchmark engineered nanomaterials; 2), assess the differences in reactivity between ENMs with the same composition (TiO_2 NM-101 vs TiO_2 DT-51); 3), assess the effect of bimetallic compositions on the surface reactivity of metal nano-oxides (monometallic vs. bimetallic); 4), calculate reactive rankings according to three dose metrics based on mass, surface area and surface sites; and 5), assess the size-dependent reactivity of a material, by comparing Co_3O_4 nanoparticles to its larger counterpart.

2 EXPERIMENTAL

2.1 Nanomaterials

All nanomaterials were used as supplied. Two anatase TiO_2 powders were compared: DT51 (CristalACTiV™) and NM-101 (labeled as JRCNM01001a by the supplier, the Joint Research Centre, JRC). In addition, two more JRC samples: CeO_2 NM-211 (JRCNM02101a) and ZnO NM-110 (JRCNM62101a), as well as four commercial samples from Sigma-Aldrich: CuO (ref. number: 544868, CuO-SA), CuFe_2O_4 (ref. number: 641723, $\text{CuFe}_2\text{O}_4\text{-SA}$), Fe_3O_4 (ref. number: 637106, $\text{Fe}_3\text{O}_4\text{-SA}$), and Co_3O_4 (ref. number: 637025, $\text{Co}_3\text{O}_4\text{-SA}$), were evaluated. **Error! Reference source not found.** summarizes data and information on these proof-of-concept samples. The size dependence of reactivity was evaluated using Co_3O_4 microparticles (ref. number: 221643, Sigma-Aldrich <10 μm).

2.2 Specific surface area

Specific surface area was calculated by the BET method with data obtained in a Micromeritics ASAP 2020 adsorption isotherm equipment. All ENMs were pretreated by degassing under vacuum for 16 h at 120 °C before nitrogen adsorption at liquid nitrogen temperature.

2.3 Methanol chemisorption and subsequent temperature-programmed surface reaction (TPSR)

Methanol chemisorption/TPSR procedure (see a detailed description in the SI, **Error! Reference source not found.**A and Figure S 2) is made on a clean dehydrated sample. 100-250 mg of nanomaterial (aggregated samples with aggregates ranging from 25 to 100 μm) were diluted with 500 mg of inert SiC (black 180, Navarro SiC S.A.), to ensure isothermal conditions, are and placed in a fixed-bed reactor (0.4 cm internal diameter). The sample is first pretreated by heating from room temperature to 450 $^{\circ}\text{C}$ at 10 $^{\circ}\text{C}/\text{min}$ in a 150 mL/min synthetic air flow and kept at this temperature for 35 min to ensure the removal of moisture and burn away impurities from its surface. After pretreatment, the sample is cooled down to 100 $^{\circ}\text{C}$ (or 50 $^{\circ}\text{C}$ for highly reactive ENMs) in synthetic air. After such treatment the surface remains hydroxylated, but not hydrated; next, the flow feed is switched to argon (100 mL/min) purge. The chemisorption temperature was optimized to prevent the formation of multilayers in the case of highly reactive materials, looking for a balance between methanol condensation at lower temperatures and methanol reaction at higher temperatures, either of which would lead to an overestimation of the surface sites.^{67,68} After purging, still at 100 $^{\circ}\text{C}$ (or 50 $^{\circ}\text{C}$ for highly reactive ENMs), 100 mL/min of 2000 ppm methanol in argon with 5% helium is fed until saturation, as determined by online mass spectrometry residual gas analysis (cf. supplementary information). The 5%helium in the argon stream is used as an internal reference for online mass spectrometry. The methanol vapor chemisorbs titrating surface hydroxyl groups; this process converts CH_3OH molecule into a chemisorbed CH_3O -moiety, the missing hydrogen atom reacts with the surface hydroxyl thus releasing an H_2O molecule per CH_3OH molecule that chemisorbs. We monitor the effluent gases by a quadrupole residual gas analyzer Pfeiffer OmniStar mass spectrometer. The m/z values followed were: CH_3OH (methanol) = 31, HCHO (formaldehyde) = 30, CH_3OCH_3 (dimethyl ether, DME) = 45, CH_3OOCH (methylformate) = 60, $(\text{CH}_3\text{O})_2\text{CH}_2$ (dimethoxy methane) = 75, H_2O (water) = 18, and CO_2 (carbon dioxide) = 44. Blank tests were performed with 500 mg of inert SiC (Figure S3). Details on the procedure, the calculation of the reactive surface sites and the surface reactions in methanol-TPSR (equations S1-5) are available in the supplementary material. This methodology is limited to thermally stable samples like metal oxides.

2.4 DTT consumption assay

DDT catalytic oxidation was performed in a batch reactor for 1h. First, a 200 $\mu\text{g}/\text{mL}$ suspension of ENM in 1 mM phosphate buffer is obtained by sonication, following

NanoGenoTox SOP (16 min at 400 W and 10% amplitude).⁶⁹ 3 mL of the ENM suspension is incubated for 1 h at 37 °C and 500 rpm with 3 mL of 100 μM DTT, obtaining a 6 mL reaction mixture with 100 μg/mL of ENM and 50 μM DTT. Then, the nanoparticles are removed by filtration, and the filtrate, with the unreacted DTT and the reaction products, is mixed with an equal volume of 1 mM Ellman's reagent (5,5'-dithiobis-(2-nitrobenzoic acid), DTNB) to quantify the non-oxidized DTT (**Error! Reference source not found.**B). Ellman's reagent reacts with the thiol groups (-SH) of the free DTT molecules, forming 5-mercapto-2-nitrobenzoic acid, a colorful complex that is measured at 412 nm by UV-Vis spectrophotometry (Shimadzu, UV-2100). In parallel, as a negative control, DTT in phosphate buffer without ENM is incubated under the same conditions and mixed with the Ellman's reagent to evaluate the DTT consumed by direct reaction without catalyst. Hydrogen peroxide 30 % (w/w) in H₂O is used as a positive control, as it provides similar DTT conversion as 1,4-naphthoquinone,⁶² being safer and not requiring filtration. All reactions were performed in triplicate. Linearity in measurements at 412 nm of DTT-DTNB nm complex was calibrated (Figure S4). DTT oxidative potential is expressed as DTT conversion (Eq. 1), as a normalized index of oxidant generation using hydrogen peroxide as a positive control (Eq. 2), or as DTT reaction rate, normalized vs. mass (Eq. 3), vs. ENM surface area (Eq. 4), or vs. number of reactive sites (Eq. 5), i.e., OxTOF.

$$\text{DTT depleted (mol \%)} = 100 - \frac{\text{Reaction absorbance}}{\text{Blank absorbance}} \cdot 100 \quad (\text{Eq. 1})$$

$$\text{NIOG (0-1)} = \frac{\text{DTT depleted by nanomaterial}}{\text{DTT depleted by positive control}} \quad (\text{Eq. 2})$$

$$\text{OP}_{\text{mass}} (\text{mol} \cdot \text{s}^{-1} \cdot \text{g}^{-1}) = \frac{\text{depleted DTT moles}}{\text{time} \cdot \text{mass of NM}} \quad (\text{Eq. 3})$$

$$\text{OP}_{\text{area}} (\mu\text{mol} \cdot \text{s}^{-1} \cdot \text{m}^{-2}) = \frac{\text{depleted DTT moles}}{\text{time} \cdot \text{surface area of NM}} \quad (\text{Eq. 4})$$

$$\text{OxTOF (s}^{-1}\text{)} = \frac{\text{depleted DTT molecules}}{\text{time} \cdot \text{active sites of NM}} \quad (\text{Eq. 5})$$

2.5 Statistical analysis

DTT OP_{mas}, OP_{area} and OxTOF are expressed as average ± sd (standard deviation). The statistical analysis was performed with SPSS 20 (IBM, Armonk, USA) using logarithmic values to obtain a better normal distribution. One-way ANOVA (Analysis of Variance) was performed to determine statistically significant differences. Subsequently, a Tukey test was

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

performed to assess pairwise differences with a significance level of $p < 0.05$ and classify ENMs according to the oxidative potential.

3 RESULTS

3.1 Surface area and reactive sites

In the series, TiO₂ NM-101 exhibits the largest BET area, 225 m²/g; the rest of ENMs have significantly lower BET values: TiO₂-DT51, 84 m²/g; CeO₂ NM-211, 76 m²/g; CuO-SA, 12 m²/g; ZnO NM-110, 9 m²/g; CuFe₂O₄-SA, 33 m²/g; Fe₃O₄-SA, 11 m²/g, and Co₃O₄-SA, 26 m²/g (**Error! Reference source not found.A**). These data are consistent with the values reported in the literature and in the supplier's technical sheets.^{70, 71, 72, 73, 74} **Error! Reference source not found.B** illustrates the specific number of sites (mmol per g). While the order of materials remains similar, the relative values change significantly between Figure 2A and B. Thus, the reactive sites surface density (site per nm²) may follow a different trend. Figure 2C shows this surface descriptor, calculated from **Error! Reference source not found.A** and B data. Interestingly, the ENMs with smaller surface area have higher reactive sites surface density: 16.6 and 21.8 sites/nm² for ZnO NM-110 and CuO-SA, respectively (values obtained at 50 °C). These data show that due to differences in site types and/or distribution, surface area and reactive sites number do not linearly correlate for these samples, as it might be erroneously assumed. It is remarkable that TiO₂-DT51, with 2.7 times lower specific surface area than TiO₂ NM-101, doubles its reactive sites surface density (14 vs. 7 sites/nm²). Therefore, BET (physical) may not be the most relevant descriptor of ENMs surface chemistry. **Error! Reference source not found. D** summarizes the trends shown in **Error! Reference source not found. A-C**, after data normalization to the most described nanomaterial in the literature: TiO₂ NM-101.

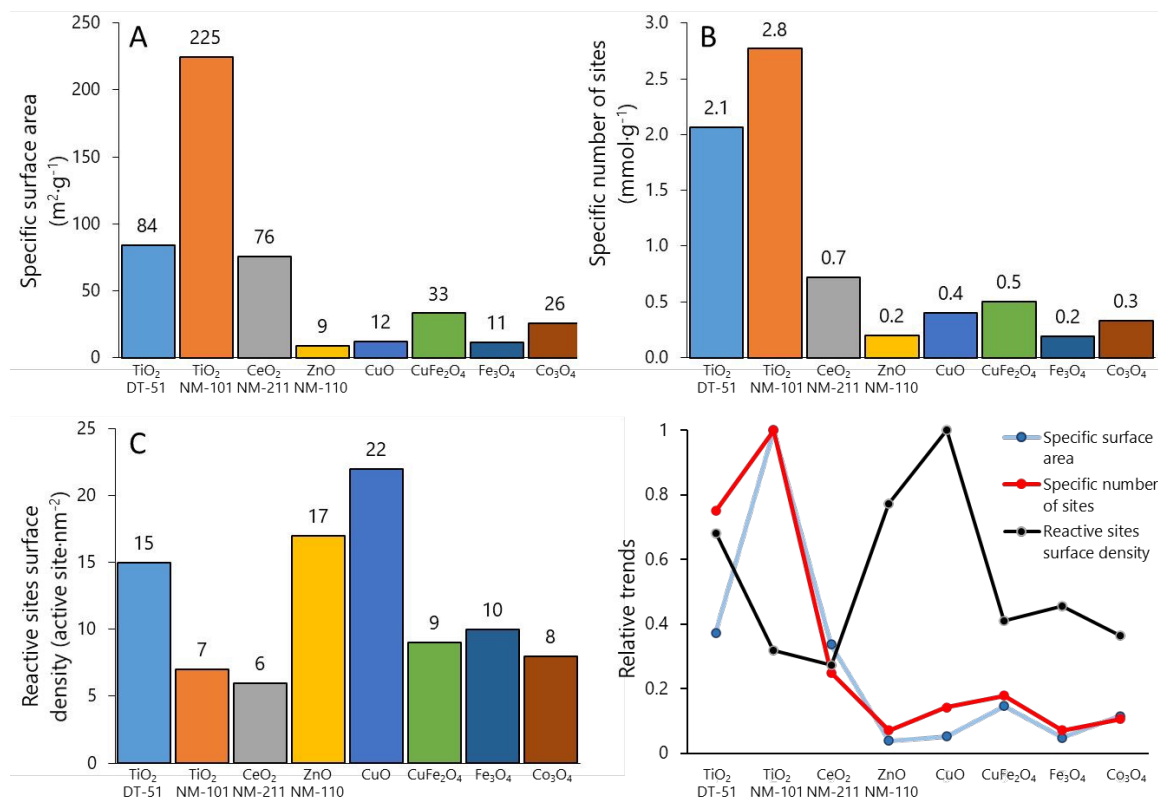


Figure 2. Surface analysis: **A)** Specific surface area obtained by N_2 adsorption isotherm, **B)** Specific number of reactive sites obtained by methanol chemisorption, **C)** Reactive sites surface density obtained by combination of A and B, **D)** Comparison of the three surface descriptors (values normalized to the maximum).

3.2 Reactive profile

The methanol TPSR profiles in **Error! Reference source not found.** provide information on the reactive sites and their reactivity. The typical TPSR products are DME, HCHO and CO_2 .

TiO₂ ENMs (DT51 and NM-101) form mainly **dimethyl ether (Error! Reference source not found. A and D)**, the characteristic product of acidic reactivity. The maximum production of dimethyl ether occurs at 349 °C for NM-101 and at 339 °C for DT51, indicating a weaker acidity of the sites of the latter, which are also fewer, as indicated by the smaller area under the curve. Redox (HCHO) and basic (CO_2) reaction products also form on both titania samples. The redox site is active in a broad temperature range, which indicates a broad

1
2
3 distribution of oxidation reactivities, and that the oxidation capacity is moderate, since rather
4 high temperatures are required to express it.
5
6

7
8 Oxidative sites produce **HCHO**. Thus, CeO₂ exhibits redox sites where methanol is oxidized
9 to formaldehyde, with a maximum near 259 °C (**Error! Reference source not found.G**);
10 ceria oxidative sites exhibit a narrower peak, which indicates that most oxidizing sites have
11 similar reactivity. This is unlike the broad distribution of oxidative site types on the titanias,
12 in the 150 to 400 °C range. Moreover, ceria has a higher oxidation capacity, for its maximum
13 is at a lower temperature than the average of HCHO formation on the titania samples.
14

15
16 ZnO NM-110, CuFe₂O₄-SA, Fe₃O₄-SA, Co₃O₄-SA and CuO-SA (**Error! Reference source**
17 **not found. C-H**) produce mainly **CO₂**, but the temperatures at which CO₂ reaches a
18 maximum differs significantly, for some it is near 220-250°C, and for others above 300°C.
19 The significantly higher maximum temperature for CO₂ production is indicative of basic
20 materials, where methoxy species adsorb strongly and can only desorb at very high
21 temperatures, thus being combusted (ZnO NM-110 and Fe₃O₄-SA). Instead, the easier
22 formation of CO₂ (some 100 °C lower temperatures) is indicative of a high oxidation capacity,
23 leading to total oxidation CO₂ rather than to partial oxidation formaldehyde (CuO-SA,
24 CuFe₂O₄-SA and Co₃O₄-SA).⁴⁹ Evaluated as a reference, micrometric Co₃O₄ (Figure S5)
25 showed a similar reactive profile than Co₃O₄ nanoparticles. Thus, the nature of the surface
26 sites in nano and micro CuO remains essentially alike, with the critical difference that a
27 minimum part of the reactive sites is exposed in the larger CuO particles, hence the risk of
28 exposure to larger CuO particles is minimized. In summary, *methanol TPSR reactive profiles*
29 *may classify materials based on a linear combination of their acidic/basic reactive profile vs.*
30 *its oxidation profile* (**Error! Reference source not found.I**). In this categorization, the X-
31 axis qualitatively indicates how oxidizing the material is, while the Y-axis moves from acidic
32 to basic character. Thus, TiO₂ DT51 and NM-101, ZnO NM-110, and Fe₂O₃-SA have a
33 moderate oxidation capacity, being Fe₂O₃-SA and ZnO NM-110 more basic and both TiO₂
34 more acidic. On the other hand, CeO₂ NM-211, Co₃O₄-SA exhibit increased oxidation
35 capacity, and the highest is for CuO-SA and CuFe₂O₄-SA.
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

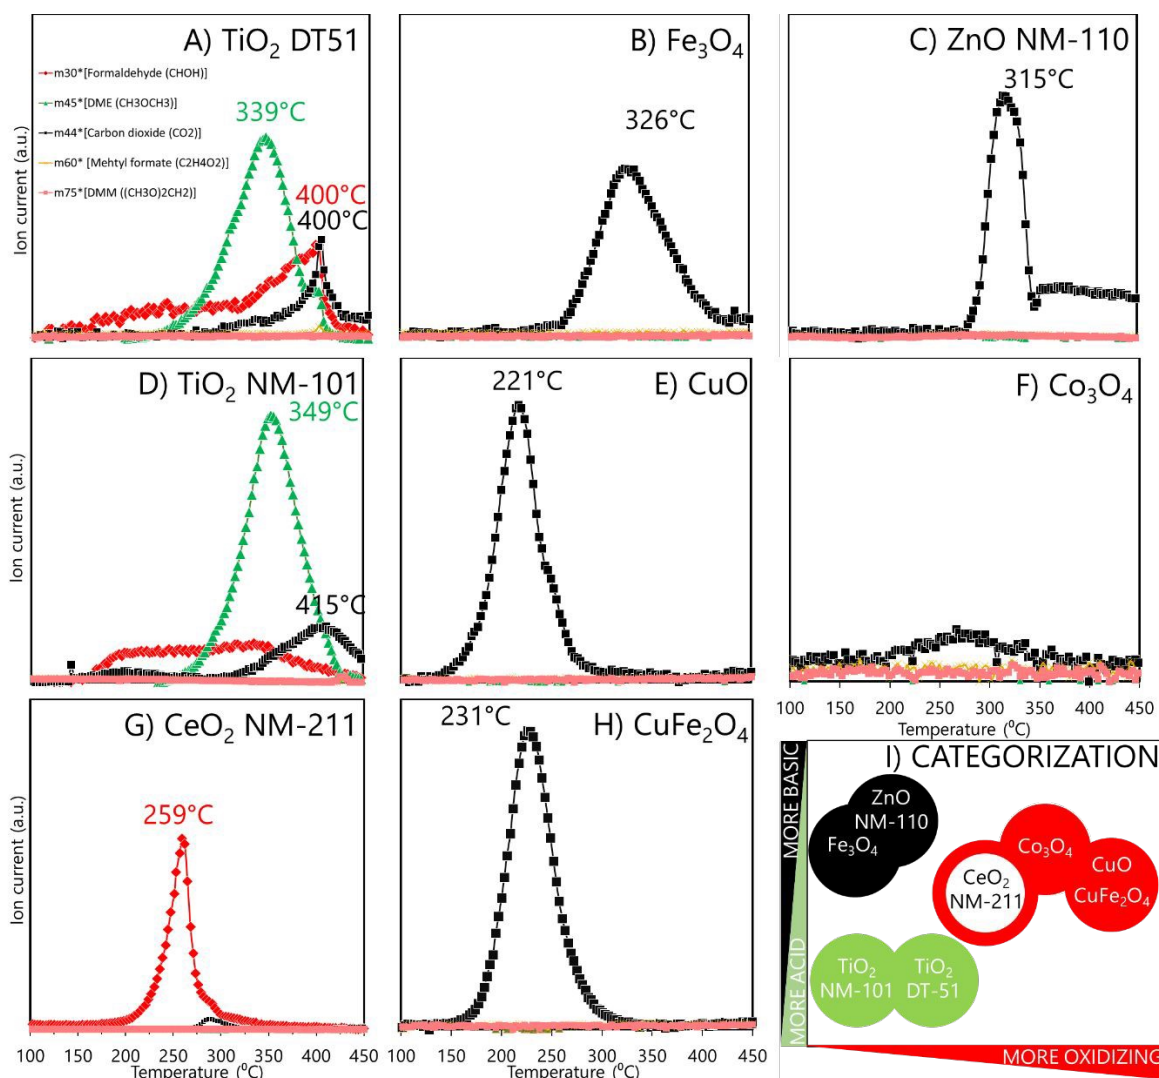


Figure 3. Temperature-programmed surface reaction products of pre-adsorbed methanol analysed by mass spectroscopy for two different anatase TiO₂: DT51 (A) and NM-101 (D), for Fe₃O₄-SA (B), for ZnO NM-110 (C), for CuO-SA (E), for Co₃O₄-SA (F) for CeO₂ NM-211 (G), and for CuFe₂O₄-SA (H). Formaldehyde signal (red) is obtained for redox sites, dimethyl ether signal (green) for acid sites, and carbon dioxide (black) for basic or high reactive redox sites. ENMs classification by MeOH-TPSR results is shown in I) with the same colour code. For a given colour, filled circles are more reactive than empty circles.

3.3 Oxidative potential

Error! Reference source not found. illustrates DDT catalytic oxidation results for 1h reaction, normalized vs. different descriptors; the corresponding classification of the ENMs based on Tukey's test using the logarithm of OP_{mass} , OP_{area} and OxTOF are provided on the right side of the plots. ZnO NM-110 was not included in the analysis because it dissolves in

the reaction media and Zn cations get complexed by DTT,⁶⁶ so no free and uncomplexed DTT is available for interaction with the ZnO NM-110 surface, and thus the results are close to the negative control.⁶⁶ The relative oxidative potential of the other ENMs significantly depends on the descriptor. The positive control normalization has little impact on the relative conversion trend (*Figure S6*), which is similar to that of the specific reaction rate shown in **Error! Reference source not found. A**: CuO-SA \approx CuFe₂O₄-SA \gg Co₃O₄-SA \approx TiO₂ NM-DT-51 \approx TiO₂ NM-101 \approx CeO₂ NM-211 $>$ Fe₃O₄-SA; according to Tukey's test, only CuO-SA and CuFe₂O₄-SA are classified as significantly highly reactive ENMs. The differences between these ENMs' reactivities are clearly amplified when the oxidation rate is normalized to the ENM surface area (**Error! Reference source not found. B**), which underlines that CuO-SA surface, being small (**Error! Reference source not found. A**), is significantly more reactive than other ENMs' surfaces in the series. Actually, Tukey's test reveals three reactivity groups of ENMs according to OP_{area} descriptor: CuO-SA $>$ Co₃O₄-SA \approx CuFe₂O₄-SA $>$ TiO₂ DT-51 \approx CeO₂ NM-211 \approx TiO₂ NM-101 \approx Fe₃O₄-SA. *Mass or BET normalizations cannot tell how reactive each site is, so this trend stands on assuming that all physical areas are equally populated by equally reactive sites, which is not the case.* Normalization per reactive site (**Error! Reference source not found. C**) delivers the OxTOF, which shows that CuO-SA and CuFe₂O₄-SA sites are the most oxidizing ones, followed by Co₃O₄-SA, and ca. fourfold more reactive than ceria sites. The remaining group of materials exhibit significantly lower oxidation activity, according to Tukey's test: CeO₂ NM-211 $>$ TiO₂ DT-51 \approx TiO₂ NM-101 \approx Fe₃O₄-SA. A larger amount of sites can make up for individual site lower reactivity; therefore, both pieces of reactivity information, global (per material dose) and individual (per site), are important to understand and classify ENMs. Among these descriptors, only OxTOF can identify with statistical significance that ceria has more reactive redox sites than titania ENMs. *From a chemical perspective, turnover frequency values may allow a better quantitative comparison of oxidative potential and provide a more accurate insight into reactivity at a molecular scale.*

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

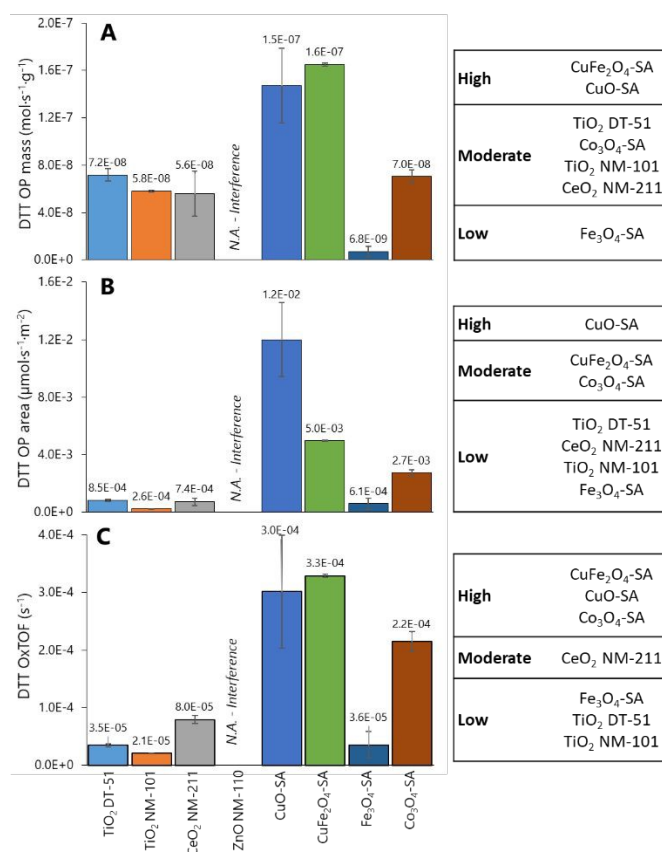


Figure 4. Oxidative potential evaluated by DTT assay and expressed as: reaction rate per mass (A), reaction rate per surface (B), oxidative turnover frequency (reaction rate per reactive site) (C). Left: Averaged OP values ($n=3$) with error bars indicating the standard deviation. Right: Statistical analysis for classification of the ENMs by OP based on Tukey' test comparison.

Size dependence of reactivity was evidenced via comparison of Co₃O₄ nanoparticles vs microparticles, which exhibited a DTT depletion of $6.7 \pm 4.2\%$ of DTT depletion, equivalent to a NIOG of 0.08 ± 0.04 , that is, around 7 times lower oxidative capacity than its nanoparticle counterpart. This is essentially due to the significantly smaller fraction of reactive sites that are exposed.

3.4 Dose metrics applied to bibliographic toxicological data

Bibliographic toxicity information for TiO₂ NM-101, CeO₂ NM-211, ZnO NM-110, CuO-SA, Fe₃O₄, CuFe₂O₄ and Co₃O₄ was extracted from eNanoMapper^{75,76} and the literature to

investigate possible correlations of the surface reactivity with in vitro toxicity descriptors (**Error! Reference source not found.**).

CuO-SA is highly toxic to pulmonary cells, causing cell death and impairing cell functions after 24-hour exposure.⁷⁷ The mechanism involves ion release, autophagy activation, and increased lipid peroxidation.^{78 79 80} Animal models support its lung inflammatory effects but do not show teratogenic potential.^{81 82} In terms of dose metrics, this ENM, the most oxidant in the series, exhibits significant effects on A549 cell viability at 5, 10 and 17.75 µg/mL gravimetric doses, equivalent to 2, 4 and 7.1 µmol/L sites doses, in different studies.⁷⁸


CuFe₂O₄-SA cytotoxic effects on human lung (A549) and liver (HepG2) cells were analyzed, illustrating a dose-dependent toxicity within a concentration range of 10–100 µg/ml (*i.e.*, 5–50 µmol site/L). Key observations include mitochondrial membrane potential (MMP) depletion, upregulation of the caspase-3 gene, and increased caspase-3 enzyme activity, suggesting apoptotic cell death as a consequence of exposure to these ENM. Furthermore, an imbalance in cellular redox status was evident through the induction of ROS and depletion of glutathione (GSH), indicating oxidative stress as a potential underlying mechanism of cytotoxicity.⁸³

ZnO NM-110, extensively studied in vitro, exhibits adverse effects in multiple cell lines, with immune system alterations observed in Raw 264.7 and MH-S macrophages (EC50: 10-25 µg/mL, *i.e.*, 3-7.5 µmol/L sites doses), pulmonary cell lines displaying cytotoxic and genotoxic effects (LC50: 76 µg/mL, that is, 22.8 µmol sites/L),^{84 85} and respiratory and male reproductive cell lines affected (EC50 < 20 µg/mL, so less than 6 µmol sites/L).⁸⁶ Hepatic damage in C3A was evidenced by WST-1 test.⁸⁷ Proteomic analysis in NRK-52E reveals pronounced effects, particularly in actin carbonylation; this ENM is classified as highly cytotoxic and a protein carbonylation agent.⁸⁸ Caco-2 cell lines exhibit cytotoxicity due to dissolved Zn²⁺, and HUVEC cell lines show reduced mitochondrial viability attributed to intracellular Zn ions and ROS. In contrast, TiO₂ NM-101 shows no cytotoxicity or inflammatory markers.^{89 90}

TiO₂ NM-101 exhibited no significant cytotoxicity in A549, HepG2, HK-2, and C3A cell lines. However, C3A cells showed IL-8 release, indicating inflammation.^{87,91} BEAS-2B cell viability

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Open Access Article. Published on 09/07/2014. Downloaded on 09/07/2014. This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



1
2
3 was unaffected by TiO₂ at concentrations of 1-100 µg/mL, i.e., 2.8-280 µmol sites/L, but
4 DNA damage and IL-6 release were observed at 10 (28 µmol sites/L) and 100 µg/mL ,
5 respectively. RAW 264.7 macrophages exposed to TiO₂ NM-101 released IL-6 and TNF-α
6 at higher concentrations (100 µg/mL).⁹²
7
8
9

10
11 The toxic mechanism of **CeO₂ NM-211** remains unclear, but protein aggregation and
12 fibrillation are proposed hypotheses.^{93, 94} CeO₂ NM-211 induced moderate pro-inflammatory
13 cytokine release in rat precision-cut lung slices (PCLuS) at 100 µg/mL, which represents a
14 sites concentration of 70 µmol/L. It is in line with other In vivo studies, where inflammatory
15 markers increased in the bronchoalveolar lavage fluid (BALF) after 14 days of exposure.^{95,96}
16 In vitro, A549 cells exposed to similar cerium oxide nanoparticles at concentrations up to
17 100 µg/mL showed no cytotoxicity.⁹⁷ In contrast, NR8383 alveolar macrophages exhibited
18 cytotoxicity at 90 µg/mL (63 µmol site/L) along with signs of inflammation, including TNF-α
19 release, after CeO₂ NM-211 exposure.⁹⁸ These results will be analyzed in section 4.2 with
20 respect to our in chemico method, as gravimetric, surface, and reactive site-based
21 concentrations offer insights into the diverse doses of ENMs in toxicology.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 **Fe₃O₄-SA** showed no adverse effects on A549 cell viability for 24-72 h for concentrations up
44 to 100 µg/mL (equivalent to 20 µmol site/L), even after being internalized within the cells
45 following 12 h exposure. Furthermore, an increase in lysosomal activity was not detected
46 after 6 h. However, a concentration-dependent decrease in mitochondrial membrane
47 potential at 100 µg/mL was statistically significant. There was no induction of pro-
48 inflammatory cytokine secretion, including IL-1β, IL-6, IL-8, and TNF-α. This evidence
49 suggests that iron oxide exhibits low cytotoxicity.⁹⁹
50
51
52
53
54
55
56
57
58
59
60

61
62
63
64
65
66
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
841
842
843
844
845
846
847
848
849
850
851
852
853
854
855
856
857
858
859
860
861
862
863
864
865
866
867
868
869
870
871
872
873
874
875
876
877
878
879
880
881
882
883
884
885
886
887
888
889
890
891
892
893
894
895
896
897
898
899
900
901
902
903
904
905
906
907
908
909
910
911
912
913
914
915
916
917
918
919
920
921
922
923
924
925
926
927
928
929
930
931
932
933
934
935
936
937
938
939
940
941
942
943
944
945
946
947
948
949
950
951
952
953
954
955
956
957
958
959
960
961
962
963
964
965
966
967
968
969
970
971
972
973
974
975
976
977
978
979
980
981
982
983
984
985
986
987
988
989
990
991
992
993
994
995
996
997
998
999
1000

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

and exposure times. These results underline the differential cellular responses to cobalt oxide nanoparticles, highlighting the enhanced sensitivity of BEAS-2B cells to cytotoxic, genotoxic, and pro-inflammatory effects.¹⁰⁰ The genotoxic effects of cobalt oxide in Chinese hamster lung fibroblast (V79) cells, primarily mediated by reactive oxygen species, were used to compare with the bulk counterparts: Co₃O₄-SA nanoparticles exhibit pronounced genotoxic effects compared to bulk Co₃O₄ macroparticles, due to significant cytotoxicity and DNA damage, attributed to enhanced ROS generation. The mitigation of genotoxic effects with N-acetylcysteine, a ROS scavenger, further confirms the central role of ROS in nanoparticle-induced toxicity. The nano-sized particles facilitate closer cellular interactions, leading to significant cytotoxicity and DNA damage from ROS, unlike the minimal interaction and impact observed with bulk materials.¹⁰¹

4 DISCUSSION

4.1 ENMs' surface sites and reactivity

The exponential increase in surface-to-volume ratio as particle size decreases to a few nanometers is crucial; additionally, quantum confinement and discrete energy levels alter electronic states and surface reactivity. We focus on the phenomenological consequences of this, not its origins. A comprehensive categorization of ENM requires an understanding of their reactivity characteristics; namely, the number of reactive surface sites, their reactive nature and relative reactivity. Nanomaterials can oxidize molecules directly or generate ROS through interactions with biological systems, which may also alter their properties. These interactions depend on the surface properties of the nanomaterials, including reactive sites beyond physical surface area. While oxidative potential is often highlighted, acidic and basic sites also significantly impact molecular interactions. Our method maps all reactive sites to provide a comprehensive description of nanomaterials and enable more reliable grouping based on their chemical surfaces. According to our data, reactivity-triggered nanotoxicity not only depends on the number and reactivity of redox sites but also on sites of basic and acidic nature. Their interplay determines how ENM's interact with the environment and with our physiology. Parameters like site-specific numbers and TOF (e.g., DTT OxTOF) are essential in elucidating the reactive potential of ENMs and linking them to potential adverse effects. Additionally, TPSR profiles provide insights into these sites' relative presence and reactivity, influencing toxicity profiles. OxTOF tendency in Figure 4C shows CuO-SA \approx CuFe₂O₄-SA > Co₃O₄-SA >> Ce₂O₃ NM-211, in line with oxidation capacity assessed by methanol-TPSR;

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

also following this correlation, the titanias, Fe₃O₄-SA and ZnO NM-110 exhibit very little methanol oxidation. Therefore, DTT probe reaction is an oxidative dehydrogenation forming a disulfide group that appears to run mechanistically parallel to the oxidative dehydrogenation of methanol to formaldehyde in TPSR experiments. The use of chemisorption avoids interference from ion release, buffer reactivity (as observed with some probe reactions in phosphate medium),¹⁰² or agglomeration that would take place in liquid-phase assays.

Reactive site surface density quantified by methanol chemisorption in our series is consistent with values reported in the literature for oxide ENMs, ranging between 0.4 and 22 sites/nm², but typically up to ca. 7 sites/nm², corresponding to a monolayer.³⁹ The high number of reactive sites on CuO-SA (22) and ZnO NM-110 (17) surfaces must be related to a highly reactive interaction with chemisorbed methoxy groups. Multilayer formation is likely on ZnO NM-110 basic sites, as suggested for La₂O₃, MgO or Cr₂O₃,³⁹ whereas CuO-SA is a highly oxidizing material that transforms surface methoxy groups into formate groups^{103,104,105}. This is consistent with the extensive CO₂ desorption profile during MeOH-TPSR. Hence, the chemisorption temperature was set to 50 °C in these materials. CO₂ formation at low temperatures on highly reactive CuO-SA is characteristic of formates decomposition, while the formation of CO₂ at high temperatures on the alkaline ZnO NM-110 is associated with the decomposition of carbonates.¹⁰⁴ The determination of reactive sites provides complementary insight to ROS determination probes, which sensitivity depends on different features. For instance, the basic character of ZnO NM-110 and its high reactive site surface density correlates with the ferric reduction ability of serum (FRAS) assay, an indirect measurement of ROS by total antioxidant depletion, and protein carbonylation assay.¹⁰⁶ In another study, electron spin resonance (ESR) spectroscopy with 3-carboxy-2,2,5,5-tetramethylpyrrolidine 1-oxyl (CPH) and 5,5-dimethyl-1-pyrroline N-oxide (DMPO) probe molecules quantifies the oxidative potential of ENMs by determining the ROS production.¹⁰⁷ Less ROS were produced by CeO₂ NM-211 and ZnO NM-110 when compared with CuO,¹⁰⁶ which agrees with our reactive ranking based in OxTOF data, and the higher number of reactive surface sites of the latter; the CPH spin probe (more sensitive to singlet oxygen, superoxide radicals, and peroxy nitrates) revealed higher ROS production by ceria than by zinc oxide, whereas the DMPO spin trap (more sensitive to hydroxyls and superoxide radicals) showed the opposite trend. Raman spectroscopy, which is highly

1
2
3 sensitive to peroxide-related species, can be used to further analyze this. *In situ*^{108,109} and
4 *operando*¹¹⁰ Raman spectra show that superoxide and peroxide species are generated at
5 the surface of different ceria materials by interaction with molecular oxygen, but there are
6 no reports of superoxide species formed at the surface of ZnO and TiO₂. Thus, reactive
7 superoxide species would only account for DMPO and CPH by CeO₂ NM-211, but not by
8 ZnO NM-110 or titania; therefore, ZnO NM-110 must generate more hydroxyls than CeO₂
9 NM-211 to account for the DMPO probe results.
10
11

12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
Titania, the least-reactive material in our series, highlights the complexity of categorizing
nanomaterials. Even with the same composition (TiO₂) and crystalline phase (anatase),
titania samples differ significantly in BET surface area, reactive site density, and
strength. TiO₂ NM-101, as measured by terephthalic acid assay, generates ROS upon
photoirradiation, but not in the dark.¹¹¹ Conversely, ROS generation detected via DMPO trap
was significantly higher than the control not only upon irradiation, but also in the dark -
although to a lesser extent.¹¹¹ Several studies on titania reactivity and photoreactivity
highlight the impact of species in biological systems (e.g., carboxylic acids, amines) that
strongly adsorb onto titania surfaces, affecting reactivity.^{102,112} This underscores the
importance of characterizing all surface reactive sites: acidic, basic, and redox. The band
gap of metal nano-oxides, crucial for correlating with oxidative stress and pulmonary
inflammation from photocatalytic ENMs, strongly depends on particle size, nuclearity, and
the nature of nearby elements, serving as an indicator of increasing quantum effects.^{113–115}

The strong influence of the titania structural variety on its surface reactivity is being
described from the perspective of nanoinformatics,^{116,117} which uses computational
approaches to understand the surface structure and reactivity of ENMs, using this data in a
FAIR (Findability, Accessibility, Interoperability and Reusability) implementation for the
nanosafety community.^{118,119}

4.2 Oxidative surface sites and *in vitro* cell viability

As *in vitro* assays monitor different effects (cell viability, protein release, inflammation, etc.)
in specific cell lines (A549, dTHP-1, etc.) and do not provide information about
biodistribution, biopersistency or biotransformation²³ of nanomaterials, they are limited in

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

predicting the overall toxicological profile, comparisons are not straightforward, and correlations with physicochemical properties of ENMs can only be done as a first approximation.^{77,120} The *in vitro* toxic effects of ENMs that over-oxidize methanol to CO₂ in TPSR and show redox surface reactivity (Co₃O₄-SA, CuFe₂O₄-SA and CuO-SA) significantly affected different cell lines,^{83,101,120} underscoring the implication of reactive surface sites in nanotoxicity field. When comparing CuO-SA and ZnO NM-110, the higher reactive sites surface density and the lower temperature of maximum methanol conversion to CO₂ of the former are indicative of a higher reactivity of CuO-SA, which correlates with the higher toxicity reported by cell viability assays with A549 line: EC₅₀ for 24 h exposure was 17.75 for CuO-SA and 76 µg/mL for ZnO NM-110.^{84,120} Site-based dose metrics underlines the higher *in vitro* toxicity of CuO-SA sites. DTT OxTOF could not be evaluated for ZnO NM-110; still, the physical-chemical properties reported in the literature -oxidation number, ionic potential, surface reducibility and redox reactivity- are consistent with its high *in vitro* toxicity.¹²¹ Nevertheless, ZnO NM-110 is a complex ENM, because its surface reactivity has biocidal properties,¹²² but its mode of action is essentially by dissolution.¹²¹

CuO-SA has the highest reactive sites surface density in the series, though not the most sites per gram, and shows the highest OxTOF (Figure 2D, Figure 4E) along with CuFe₂O₄-SA. This correlates with their inflammatory effects, commonly associated with ROS generation and oxidative stress, making these ENMs the most toxic in the series.¹²³ CuO-SA's oxidative damage was evaluated in HepG2 cells, with endocytosis transporting nanoparticles to endo/lysosomes, leading to lysosome disruption and copper ion overload.¹²⁴ This mechanism may involve surface reactivity, initially overlooked due to lack of information on reactive sites. CuO-SA induced oxidative changes in A549 cells, increasing protein carbonylation, oxidizing protein thiols, and decreasing cell viability, with no effects from dissolved copper ions.¹²⁵ These effects were more pronounced in CuO-SA with higher crystalline defects and ROS production, likely due to higher reactive sites surface density.¹²⁵ Other studies reported CuO-SA's distinct cytotoxicity in A549 and HeLa S3 cells from direct interactions with cellular components, facilitated by greater surface area and reactive sites density compared to microparticles. This parameter could facilitate the surface interactions of CuO-SA with their surroundings. For that reason, elevated intracellular levels can disrupt copper homeostasis, leading to pro-oxidative reactions¹²⁶ produced at the surface of CuO-SA nanoparticles.¹²⁷

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Co₃O₄-SA nanoparticles exhibited higher reactivity for DTT depletion than bulk material, reflected in genotoxic effects V79 cells, primarily mediated by reactive oxygen species. This indicates that nano-sized Co₃O₄-SA induces significant cytotoxicity and DNA damage, unlike larger particles.¹⁰¹ The toxicity of TiO₂ NM-101 is not fully understood due to inconsistent evidence across different tests.

In the case of CeO₂, the literature has typically linked its toxicity with reactive oxygen species generation and the Ce³⁺/Ce⁴⁺ ratio,¹²⁸ related to the exposed phase of ceria^{129,130} and its defects, which is also key for catalytic activity.¹⁰⁸ These properties can be easily determined by several techniques^{131–135} CeO₂ NM-211, with redox surface sites and moderate oxidative capacity, causes cell death by apoptosis and DNA damage in pulmonary cell lines.^{136,137} The OxTOF of CeO₂ NM-211 is between those of the titania ENMs and of CuO-SA, despite its low BET. This is consistent with the intense formaldehyde production in MeOH-TPSR, maximum at 259 °C, and with characterization reported in the literature: CeO₂ NM-211 surface contains 22% Ce (III) (XPS), indicative of redox sites, which induce ROS generation, as detected by ESR.^{131–135} CeO₂ is highly oxidizing, while defect-rich CeO_{2-x} has antioxidant properties. This versatility is used to engineer ceria nanoparticles by tuning its properties.^{138,139} and, thus, its performance e.g. in catalysis, from combustion to selective oxidation^{131,140,141}, and in biomedical applications, from biocidal to antioxidant^{138,139,142}. The dynamic states of ceria nanomaterials in aqueous media¹⁴³ or biological media^{132,144,145} resulting in defective ceria are extensively investigated¹⁴⁶.

ZnO NM-110, which induces protein carbonylation,¹⁴⁷ has high reactive site surface density, facilitating the formation of a protein corona. This aligns with reports on BSA-ZnO interactions, which demonstrate that protein adsorption on ZnO NM-110 surface is higher compared to other ENMs like TiO₂ NM-110.⁸⁴ Despite TiO₂ NM-110 having a larger surface area, its reactive sites surface density is lower than that of ZnO NM-110.

Titania and iron oxide exhibit the lowest reactivity. Fe₃O₄-SA showed no adverse effects even after being internalized within the cells following 12 h exposure. Similarly, both titania samples convert methanol into carbon dioxide, but above 400 °C and to a limited extent, as they are essentially acidic. This low redox reactivity is consistent with their low DTT OxTOF.

*In line with our hypothesis, the high BET area of TiO₂ NM-101 does not directly correlate with adverse effects. While it has a high surface area (a physical feature) its chemical reactive profile counterpart does not run in parallel. The number of surface reactive sites is low, and their reactivity is moderate. TiO₂ NM-101 is a relatively safe ENM, with no cytotoxicity for cell viability in immune, hepatic, reproductive and pulmonary cell lines such as A549, HepG2, HK-2 or C3A. There are no toxicological data for TiO₂-DT51, but the lower number and reactivity of its sites predicts that DT51 would be safer than NM-101. Fe₃O₄, classified as low redox reactive via DTT OxTOF, is described as a safe ENM in terms of *in vitro* evaluation in the literature.⁹⁹*

An *in chemico* classification of ENMs can thus be proposed based on methanol chemisorption, reactivity of surface sites and DTT Oxidative Turnover Frequency that may correlate with *in vitro* toxicity sites-based dose metrics: $CuO-SA \approx CuFe_2O_4-SA > Co_3O_4-SA \approx ZnO\ NM-110 \gg CeO_2\ NM-211 \geq Fe_3O_4-SA \approx TiO_2\ NM-110$

4.3 Reactive surface site-based dose metrics

Recently, some works emphasized the critical importance of adopting dose metrics that reflect the relevance of surface and particle number when assessing the nanotoxicity of ENMs, as traditional mass-based dose metrics are insufficient for evaluating the unique toxicological responses of nanoscale particles.^{148,149} These studies collectively underscore the need for more accurate dose metrics to assess the potential risks associated with ENMs. Due to the assumption that not all physical areas are equally populated by equally reactive sites, the reactive sites concentration is proposed as a tool to better quantify the ENMs exposition. For example, TiO₂ NM-101 has 4 times higher specific number of reactive sites than CeO₂ NM-211 (2.8 vs 0.7 mmol/g), but also 3 times higher surface area, so the reactive sites surface density is only slightly higher for the titania (7 vs. 6 sites/nm²), and therefore the comparison is similar by DTT OxTOF and by OP_{area} : TiO₂ NM-101 has 3-4 times less oxidative potential than CeO₂ NM-211. A different impression is provided by OP_{mass} . Hence, while mass or physical surface area do not provide a site-relevant dose metrics, the number of reactive sites connects with reactivity-triggered effects. This may serve as a new possible dose metrics as an approach to assess the exposure to nanomaterials. The differences are greater when TiO₂ NM-101 is compared to CuO-SA, with very low specific surface area, and thus high reactive sites surface density. These are much more reactive than those of titania

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

and ceria, as observed by DTT OxTOF; but not as much as OP_{area} indicates. Moreover, a dose metrics based on reactive sites underscores that CuO-SA, with a dose of sites of 4 $\mu\text{mol/L}$, is capable of producing a significant adverse effect in A549, while 280 $\mu\text{mol/L}$ of titania sites did not significantly decrease cell viability.

5 CONCLUSIONS AND OUTLOOK

Reactive-based nanotoxicity is primarily governed by the surface chemistry of engineered nanomaterials, making catalysis science principles highly relevant to describing the reactive nature of ENMs. Our findings conclude that 1) The specific surface area does not reliably correlate with nanomaterial reactivity, necessitating consideration of surface sites quantity, nature, and reactivity for categorization and site-specific dosing; 2) this can be achieved by a new approach methodology that quantifies and describes reactive surface sites by chemisorption and reaction tests with probe molecules. 3) Methanol offers a triple benefit: it quantifies surface sites through chemisorption, characterizes surface reactivity (acidic, basic, or redox) via temperature-programmed surface reaction, and overcomes limitations of liquid-phase reactions, such as possible ion release, pH-dependent agglomeration, effects of the dispersion protocol, or stability issues, providing insights into the primary reactivity of thermally-stable nanomaterials such as metal oxides. 4) Combining site quantification with physiologically relevant oxidation reactions, like DTT, allows for calculating site-specific oxidative reactivity (OxTOF), aiding nanomaterial classification: CuO-SA, CuFe₂O₄-SA, Co₃O₄-SA are the most oxidizing ENMs, according to a higher *in vitro* toxicity, while less reactive ENMs does not produce adverse effects in *in vitro* models.

CuO-SA, CuFe₂O₄-SA, Co₃O₄-SA, Fe₃O₄-SA, ZnO NM-110, CeO₂ NM-211 and two TiO₂ ENMs (DT51 and NM-101) are ranked into three categories with statistically different reactivity based on DTT. This fundamental site-specific reactivity information is a relevant descriptor to group ENMs and, ultimately, understand nanotoxicity. Moreover, the behavior of a given material not only depends on its specific nanoform (e.g., crystallinity, size, band gap, solubility, hydrophobicity, surface charge, aspect ratio or shape), but also on its chemical reactive features, like the number of surface reactive sites, their nature, their reactivity and their relative populations. In another cases, the adverse effect would not appear related to the reactivity but to other features, like in multiwalled carbon nanotubes.¹⁵⁰

This new methodology offers a complementary *in chemico* approach to unravel nanomaterial modes of action. To validate its effectiveness, further testing with additional reference and real-life ENMs and relevant and comparable toxicity information is essential. On a broader vista, the correlation with cellular assays will help establish molecular insight into the reactive basis of nanotoxicity. There are, however, significant structure, reactivity and toxicity data gaps to connect adverse effects with chemical reactivity. This approach aims to elucidate the specific pathways impacted by ENMs, highlighting their role in achieving a comprehensive understanding of nanomaterial toxicity and advocating for safe-by-design principles. Filling these data gaps is in the mission of nanoinformatics and nanosafety projects, supported by platforms like eNanoMapper. Mapping all reactive properties enables a more relevant grouping of nanomaterials since the acidic, basic and redox properties not only reflect their reactivity for adverse effects but also for interaction with species and molecules in biological systems.

6 ACKNOWLEDGMENTS

The authors acknowledge the financial support by the European Commission H2020 project NanoInformaTIX (GA 81446). JRC reference materials were supplied by Dr. Juan Riego Sintés at JRC-Ispra.

7 AUTHOR CONTRIBUTIONS

M. A. Bañares: Conceptualization, original idea, supervision, writing-original draft preparation; V. Alcolea-Rodriguez.: data curation, writing-original draft preparation, investigation, statistical analysis, experimental methodology; R. Portela: Analysis, planning, supervision, writing-original draft preparation. V. Calvino-Casilda: reviewing and editing

All authors equally contributed to the writing.

8 AUTHORS' FULL NAME, ORCID, E-MAIL, CONTRIBUTIONS:

1. V. Alcolea-Rodriguez <https://orcid.org/0000-0002-2392-0817> victor.alcolea@csic.es
2. Raquel Portela: <http://orcid.org/0000-0002-1882-4759> raquel.portela@csic.es
3. Miguel A. Bañares: <http://orcid.org/0000-0003-3875-4468> miguel.banares@csic.es
4. V. Calvino-Casilda <https://orcid.org/0000-0002-2756-2164> vcalvino@ieec.uned.es



All authors have given approval to the final version of the manuscript.
The authors declare no competing financial interest.

9 REFERENCES

- 1 Serrano-Lotina A, Portela R, Baeza P, Alcolea-Rodriguez V, Villarroel M, Ávila P. Zeta potential as a tool for functional materials development. *Catal Today* 2022. doi:10.1016/j.cattod.2022.08.004.
- 2 Pacchioni G. Oxygen Vacancy: The Invisible Agent on Oxide Surfaces. *ChemPhysChem* 2003; **4**: 1041–1047.
- 3 European Commission, Joint Research Centre, Rauscher H, Kestens V, Rasmussen K, Linsinger T, Stefaniak E. Guidance on the implementation of the Commission Recommendation 2022/C 229/01 on the definition of nanomaterial. *Publications Office of the European Union* 2023. doi:10.2760/237496.
- 4 Kasemets K, Ivask A, Dubourguier HC, Kahru A. Toxicity of nanoparticles of ZnO, CuO and TiO₂ to yeast *Saccharomyces cerevisiae*. *Toxicology in Vitro* 2009; **23**: 1116–1122.
- 5 Nel A, Xia T, Mädler L, Li N. Toxic Potential of Materials at the Nanolevel. *Science (1979)* 2006; **311**: 622–627.
- 6 Buzea C, Pacheco II, Robbie K. Nanomaterials and nanoparticles: Sources and toxicity. *Biointerphases* 2007; **2**: MR17–MR71.
- 7 Talebian S, Rodrigues T, Das Neves J, Sarmiento B, Langer R, Conde J. Facts and Figures on Materials Science and Nanotechnology Progress and Investment. *ACS Nano* 2021; **15**: 15940–15952.
- 8 Khan I, Saeed K, Khan I. Nanoparticles: Properties, applications and toxicities. *Arabian Journal of Chemistry* 2017. doi:10.1016/j.arabjc.2017.05.011.
- 9 Kinneer C, Moore TL, Rodriguez-Lorenzo L, Rothen-Rutishauser B, Petri-Fink A. Form Follows Function: Nanoparticle Shape and Its Implications for Nanomedicine. *Chem Rev* 2017; **117**: 11476–11521.
- 10 Haase, A. & Klaessig, F., (2018). EU US Roadmap Nanoinformatics 2030. EU Nanosafety Cluster. <https://doi.org/10.5281/zenodo.1486012>. doi:10.5281/zenodo.1486012.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
- 11 Jeliaskova N, Apostolova MD, Andreoli C, Barone F, Barrick A, Battistelli C *et al.* Towards FAIR nanosafety data. *Nat Nanotechnol* 2021; **16**: 644–654.
- 12 Singh AV, Laux P, Luch A, Sudrik C, Wiehr S, Wild AM *et al.* Review of emerging concepts in nanotoxicology: opportunities and challenges for safer nanomaterial design. *Toxicol Mech Methods* 2019; **29**: 378–387.
- 13 Manke A, Wang L, Rojanasakul Y. Mechanisms of Nanoparticle-Induced Oxidative Stress and Toxicity. *Biomed Res Int* 2013; **2013**: 1–15.
- 14 Choi H, Choi B, Han J, Shin HE, Park W, Kim D. Reactive Oxygen Species Responsive Cleavable Hierarchical Metallic Supra-Nanostructure. *Small* 2022; **18**. doi:10.1002/sml.202202694.
- 15 Schwarz-Plaschg C, Kallhoff A, Eisenberger I. Making Nanomaterials Safer by Design? *Nanoethics* 2017; **11**: 277–281.
- 16 Jeliaskova N, Bleeker E, Cross R, Haase A, Janer G, Peijnenburg W *et al.* How can we justify grouping of nanoforms for hazard assessment? Concepts and tools to quantify similarity. *NanoImpact* 2022; **25**: 100366.
- 17 Kraegeloh A, Suarez-Merino B, Sluijters T, Micheletti C. Implementation of safe-by-design for nanomaterial development and safe innovation: Why we need a comprehensive approach. *Nanomaterials* 2018; **8**. doi:10.3390/nano8040239.
- 18 Bañares MA, Haase A, Tran L, Lobaskin V, Oberdörster G, Rallo R *et al.* CompNanoTox2015: novel perspectives from a European conference on computational nanotoxicology on predictive nanotoxicology. *Nanotoxicology* 2017; **11**: 839–845.
- 19 Stone V, Gottardo S, Bleeker EAJ, Braakhuis H, Dekkers S, Fernandes T *et al.* A framework for grouping and read-across of nanomaterials- supporting innovation and risk assessment. *Nano Today* 2020; **35**: 1–15.
- 20 Verdon R, Stone V, Murphy F, Christopher E, Johnston H, Doak S *et al.* The application of existing genotoxicity methodologies for grouping of nanomaterials: towards an integrated approach to testing and assessment. *Part Fibre Toxicol* 2022; **19**: 1–9.
- 21 Murphy FA, Johnston HJ, Dekkers S, Bleeker EAJ, Oomen AG, Fernandes TF *et al.* How to formulate hypotheses and IATAs to support grouping and read-across of nanoforms. *ALTEX* 2023; **40**: 125–140.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22 Sintes JR, Blázquez M, Moya S, Socorro Vazquez. Safety Issues and Regulatory Challenges of Nanomaterials A. 2012 doi:10.2788/76363.
- 23 Setyawati MI, Zhao Z, Ng KW. Transformation of Nanomaterials and Its Implications in Gut Nanotoxicology. *Small* 2020; **16**: 1–17.
- 24 Shirokii N, Din Y, Petrov I, Seregin Y, Sirotenko S, Razlivina J *et al.* Quantitative Prediction of Inorganic Nanomaterial Cellular Toxicity via Machine Learning. *Small* 2023; **19**: 1–7.
- 25 Godwin H, Nameth C, Avery D, Bergeson LL, Bernard D, Beryt E *et al.* Nanomaterial Categorization for Assessing Risk Potential To Facilitate Regulatory Decision-Making. *ACS Nano* 2015; **9**: 3409–3417.
- 26 Lynch I, Weiss C, Valsami-Jones E. A strategy for grouping of nanomaterials based on key physico-chemical descriptors as a basis for safer-by-design NMs. *Nano Today* 2014; **9**: 266–270.
- 27 Fischer I, Milton C, Wallace H. Toxicity testing is evolving! *Toxicol Res (Camb)* 2020; **9**: 67–80.
- 28 Schmeisser S, Miccoli A, von Bergen M, Berggren E, Braeuning A, Busch W *et al.* New approach methodologies in human regulatory toxicology – Not if, but how and when! *Environ Int* 2023; **178**: 108082.
- 29 Doak SH, Clift MJD, Costa A, Delmaar C, Gosens I, Halappanavar S *et al.* The Road to Achieving the European Commission’s Chemicals Strategy for Nanomaterial Sustainability—A PATROLS Perspective on New Approach Methodologies. *Small* 2022; **18**. doi:10.1002/smll.202200231.
- 30 Bahl A, Ibrahim C, Plate K, Haase A, Dengjel J, Nymark P *et al.* PROTEOMAS: a workflow enabling harmonized proteomic meta-analysis and proteomic signature mapping. *J Cheminform* 2023; **15**: 1–17.
- 31 Padmore T, Stark C, Turkevich LA, Champion JA. Quantitative analysis of the role of fiber length on phagocytosis and inflammatory response by alveolar macrophages. *Biochimica et Biophysica Acta (BBA) - General Subjects* 2017; **1861**: 58–67.
- 32 Boyles MSP, Young L, Brown DM, MacCalman L, Cowie H, Moisala A *et al.* Multi-walled carbon nanotube induced frustrated phagocytosis, cytotoxicity and pro-inflammatory conditions in macrophages are length dependent and greater than that of asbestos. *Toxicology in Vitro* 2015; **29**: 1513–1528.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33 Nel A, Xia T, Meng H, Wang X, Lin S, Ji Z *et al.* Nanomaterial toxicity testing in the
21st century: Use of a predictive toxicological approach and high-throughput
screening. *Acc Chem Res* 2013; **46**: 607–621.
- 34 Hsieh S, Bello D, Schmidt DF, Pal AK, Stella A, Isaacs JA *et al.* Mapping the Biological
Oxidative Damage of Engineered Nanomaterials. *Small* 2013; **9**: 1853–1865.
- 35 Halappanavar S, Van Den Brule S, Nymark P, Gaté L, Seidel C, Valentino S *et al.*
Adverse outcome pathways as a tool for the design of testing strategies to support
the safety assessment of emerging advanced materials at the nanoscale. *Part Fibre
Toxicol* 2020; **17**: 1–24.
- 36 Gerloff K, Landesmann B, Worth A, Munn S, Palosaari T, Whelan M. The Adverse
Outcome Pathway approach in nanotoxicology. *Computational Toxicology* 2017; **1**:
3–11.
- 37 Labib S, Williams A, Yauk CL, Nikota JK, Wallin H, Vogel U *et al.* Nano-risk Science:
Application of toxicogenomics in an adverse outcome pathway framework for risk
assessment of multi-walled carbon nanotubes. *Part Fibre Toxicol* 2016; **13**: 1–17.
- 38 Cronin MTD, Bajot F, Enoch SJ, Madden JC, Roberts DW, Schwöbel J. The in
chemico-in silico interface: Challenges for integrating experimental and
computational chemistry to identify toxicity. *ATLA Alternatives to Laboratory Animals*
2009; **37**: 513–521.
- 39 Wachs IE. Number of surface sites and turnover frequencies for oxide catalysts. *J
Catal* 2022; **405**: 462–472.
- 40 Lwin S, Li Y, Frenkel AI, Wachs IE. Nature of WO_x Sites on SiO₂ and Their Molecular
Structure-Reactivity/Selectivity Relationships for Propylene Metathesis. *ACS Catal*
2016; **6**: 3061–3071.
- 41 J. M. Thomas, W. J. Thomas NY. *Principles and practice of heterogeneous catalysis*.
VCH (1997). Page 27.
- 42 Briand LE, Hirt AM, Wachs IE. Quantitative determination of the number of surface
active sites and the turnover frequencies for methanol oxidation over metal oxide
catalysts: Application to bulk metal molybdates and pure metal oxide catalysts. *J
Catal* 2001; **202**: 268–278.
- 43 Kulkarni D, Wachs IE. Isopropanol oxidation by pure metal oxide catalysts: Number
of active surface sites and turnover frequencies. *Appl Catal A Gen* 2002; **237**: 121–
137.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 44 Briand LE, Jehng JM, Cornaglia L, Hirt AM, Wachs IE. Quantitative determination of the number of surface active sites and the turnover frequency for methanol oxidation over bulk metal vanadates. *Catal Today* 2003; **78**: 257–268.
- 45 Gates BC. *Catalytic chemistry*. 1991.
- 46 Tatibouët JM. Methanol oxidation as a catalytic surface probe. *Appl Catal A Gen* 1997; **148**: 213–252.
- 47 Jehng J-M, Wachs IE, Ford M. Temperature-Programmed (TP) Techniques. In: *Springer Handbook of Advanced Catalyst Characterization*. Springer Handb. Chapter 45. 2023, pp 1005–1029.
- 48 Wu Y, Gao F, Wang H, Kovarik L, Sudduth B, Wang Y. Probing Acid–Base Properties of Anatase TiO₂ Nanoparticles with Dominant {001} and {101} Facets Using Methanol Chemisorption and Surface Reactions. *The Journal of Physical Chemistry C* 2021; **125**: 3988–4000.
- 49 Jehng JM, Wachs IE, Patience GS, Dai YM. Experimental methods in chemical engineering: Temperature programmed surface reaction spectroscopy—TPSR. *Canadian Journal of Chemical Engineering* 2021; **99**: 423–434.
- 50 Daellenbach KR, Uzu G, Jiang J, Cassagnes LE, Leni Z, Vlachou A *et al*. Sources of particulate-matter air pollution and its oxidative potential in Europe. *Nature* 2020; **587**: 414–419.
- 51 Janssen NAH, Yang A, Strak M, Steenhof M, Hellack B, Gerlofs-Nijland ME *et al*. Oxidative potential of particulate matter collected at sites with different source characteristics. *Science of the Total Environment* 2014; **472**: 572–581.
- 52 Gao D, Ripley S, Weichenthal S, Godri Pollitt KJ. Ambient particulate matter oxidative potential: Chemical determinants, associated health effects, and strategies for risk management. *Free Radic Biol Med* 2020; **151**: 7–25.
- 53 Breznan D, Nazemof N, Kunc F, Hill M, Vladisavljevic D, Gomes J *et al*. Acellular oxidative potential assay for screening of amorphous silica nanoparticles. *Analyst* 2020; **145**: 4867–4879.
- 54 Rao L, Zhang L, Wang X, Xie T, Zhou S, Lu S *et al*. Oxidative potential induced by ambient particulate matters with acellular assays: A review. *Processes* 2020; **8**: 1–21.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
66
- Kramer AL, Dorn S, Perez A, Roper C, Titley IA, Cayton K *et al.* Assessing the oxidative potential of PAHs in ambient PM_{2.5} using the DTT consumption assay. *Environmental Pollution* 2021; **285**: 117411.
- Jeevanandam J, Barhoum A, Chan YS, Dufresne A, Danquah MK. Review on nanoparticles and nanostructured materials: History, sources, toxicity and regulations. *Beilstein Journal of Nanotechnology* 2018; **9**: 1050–1074.
- Yang H, Liu C, Yang D, Zhang H, Xi Z. Comparative study of cytotoxicity, oxidative stress and genotoxicity induced by four typical nanomaterials: The role of particle size, shape and composition. *Journal of Applied Toxicology* 2009; **29**: 69–78.
- Setyawati MI, Tay CY, Leong DT. Effect of zinc oxide nanomaterials-induced oxidative stress on the p53 pathway. *Biomaterials* 2013; **34**: 10133–10142.
- Čapek J, Roušar T. Detection of oxidative stress induced by nanomaterials in cells—the roles of reactive oxygen species and glutathione. *Molecules* 2021; **26**. doi:10.3390/molecules26164710.
- Mendoza RP, Brown JM. Engineered nanomaterials and oxidative stress: Current understanding and future challenges. *Curr Opin Toxicol* 2019; **13**: 74–80.
- Crobeddu B, Aragao-Santiago L, Bui LC, Boland S, Baeza Squiban A. Oxidative potential of particulate matter 2.5 as predictive indicator of cellular stress. *Environmental Pollution* 2017; **230**: 125–133.
- Jiang H, Sabbir Ahmed CM, Canchola A, Chen JY, Lin YH. Use of dithiothreitol assay to evaluate the oxidative potential of atmospheric aerosols. *Atmosphere (Basel)* 2019; **10**: 1–21.
- Øvrevik J. Oxidative Potential Versus Biological Effects: A Review on the Relevance of Cell-Free/Abiotic Assays as Predictors of Toxicity from Airborne Particulate Matter. *Int J Mol Sci* 2019; **20**: 4772.
- Crobeddu B, Baudrimont I, Deweirtdt J, Sciare J, Badel A, Camproux AC *et al.* Lung Antioxidant Depletion: A Predictive Indicator of Cellular Stress Induced by Ambient Fine Particles. *Environ Sci Technol* 2020; **54**: 2360–2369.
- Sauvain JJ, Deslarzes S, Riediker M. Nanoparticle reactivity toward dithiothreitol. *Nanotoxicology* 2008; **2**: 121–129.
- Sauvain JJ, Rossi MJ, Riediker M. Comparison of three acellular tests for assessing the oxidation potential of nanomaterials. *Aerosol Science and Technology* 2013; **47**: 218–227.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 67 Briand LE, Hirt AM, Wachs IE. Quantitative determination of the number of surface active sites and the turnover frequencies for methanol oxidation over metal oxide catalysts: Application to bulk metal molybdates and pure metal oxide catalysts. *J Catal* 2001; **202**: 268–278.
- 68 Wachs IE. Number of surface sites and turnover frequencies for oxide catalysts. *J Catal* 2022; **405**: 462–472.
- 69 Jensen KA. NanoGenoTox. WP4, Deliverable 3: Final protocol for producing suitable MN exposure media. The generic NANOGENOTOX dispersion protocol. Standard Operation Procedure (SOP) and background documentation. 2011.
- 70 JRC NANOMATERIALS REPOSITORY. List of Representative Nanomaterials. 2016.
- 71 Rasmussen K, Mast J, Temmerman P De, Verleysen E, Waegeneers N, Steen F Van *et al.* *Titanium Dioxide, NM-100, NM-101, NM-102, NM-103, NM-104, NM-105: Characterisation and Physico- Chemical Properties*. 2014 doi:10.2788/79554.
- 72 Singh C, Europäische Kommission Gemeinsame Forschungsstelle Institute for Health and Consumer Protection. *Cerium Dioxide NM-211, NM-212, NM-213, characterisation and test item preparation JRC repository: NM-series of representative manufactured nanomaterials*. 2014 doi:10.2788/80203.
- 73 Singh C, Friedrichs S, Levin M, Birkedal R, Jensen KA, Pojana G *et al.* *Zinc Oxide NM-110, NM-111, NM-112, NM-113 Characterisation and Test Item Preparation*. 2011 doi:10.2787/55008.
- 74 Martín-Gómez J, Hidalgo-Carrillo J, Montes V, Estévez-Toledano RC, Escamilla JC, Marinas A *et al.* EPR and CV studies cast further light on the origin of the enhanced hydrogen production through glycerol photoreforming on CuO:TiO₂ physical mixtures. *J Environ Chem Eng* 2021; **9**: 105336.
- 75 Kochev N, Jeliaskova N, Paskaleva V, Tancheva G, Iliev L, Ritchie P *et al.* Your spreadsheets can be fair: A tool and fairification workflow for the enanomapper database. *Nanomaterials* 2020; **10**: 1–23.
- 76 Hastings J, Jeliaskova N, Owen G, Tsiliki G, Munteanu CR, Steinbeck C *et al.* eNanoMapper: Harnessing ontologies to enable data integration for nanomaterial risk assessment. *J Biomed Semantics* 2015; **6**: 1–15.
- 77 Moschini E, Colombo G, Chirico G, Capitani G, Dalle-Donne I, Mantecca P. Biological mechanism of cell oxidative stress and death during short-term exposure to nano CuO. *Sci Rep* 2023; **13**: 2326.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 78 Moschini E, Gualtieri M, Colombo M, Fascio U, Camatini M, Mantecca P. The modality of cell-particle interactions drives the toxicity of nanosized CuO and TiO₂ in human alveolar epithelial cells. *Toxicol Lett* 2013; **222**: 102–116.
- 79 Semisch A, Ohle J, Witt B, Hartwig A. Cytotoxicity and genotoxicity of nano - and microparticulate copper oxide: role of solubility and intracellular bioavailability. *Part Fibre Toxicol* 2014; **11**: 10.
- 80 Kwon J-T, Kim Y, Choi S, Yoon B, Kim H-S, Shim I *et al.* Pulmonary Toxicity and Proteomic Analysis in Bronchoalveolar Lavage Fluids and Lungs of Rats Exposed to Copper Oxide Nanoparticles. *Int J Mol Sci* 2022; **23**: 13265.
- 81 Perelshtein I, Lipovsky A, Perkas N, Gedanken A, Moschini E, Mantecca P. The influence of the crystalline nature of nano-metal oxides on their antibacterial and toxicity properties. *Nano Res* 2015; **8**: 695–707.
- 82 Mouche I, Malésic L, Gillardeaux O. FETAX assay for evaluation of developmental toxicity. *Methods in Molecular Biology* 2017; **1641**: 311–324.
- 83 Ahmad J, Alhadlaq HA, Alshamsan A, Siddiqui MA, Saquib Q, Khan ST *et al.* Differential cytotoxicity of copper ferrite nanoparticles in different human cells. *Journal of Applied Toxicology* 2016; **36**: 1284–1293.
- 84 Precupas A, Gheorghe D, Botea-Petcu A, Leonties AR, Sandu R, Popa VT *et al.* Thermodynamic Parameters at Bio-Nano Interface and Nanomaterial Toxicity: A Case Study on BSA Interaction with ZnO, SiO₂, and TiO₂. *Chem Res Toxicol* 2020; **33**: 2054–2071.
- 85 Yamani N El, Collins AR, Rundén-Pran E, Fjellsbø LM, Shaposhnikov S, Zienolddiny S *et al.* In vitro genotoxicity testing of four reference metal nanomaterials, titanium dioxide, zinc oxide, cerium oxide and silver: Towards reliable hazard assessment. *Mutagenesis* 2017; **32**: 117–126.
- 86 Farcas L, Andón FT, Di Cristo L, Rotoli BM, Bussolati O, Bergamaschi E *et al.* Comprehensive in vitro toxicity testing of a panel of representative oxide nanomaterials: First steps towards an intelligent testing strategy. *PLoS One* 2015; **10**: 1–34.
- 87 Kermanizadeh A, Pojana G, Gaiser BK, Birkedal R, Bilaničová D, Wallin H *et al.* In vitro assessment of engineered nanomaterials using a hepatocyte cell line: Cytotoxicity, pro-inflammatory cytokines and functional markers. *Nanotoxicology* 2013; **7**: 301–313.

- 1
2
3
4 88 Driessen MD, Mues S, Vennemann A, Hellack B, Bannuscher A, Vimalakanthan V *et al.* Proteomic analysis of protein carbonylation: A useful tool to unravel nanoparticle toxicity mechanisms. *Part Fibre Toxicol* 2015; **12**: 1–18.
- 5
6
7
8 89 Cao Y, Roursgaard M, Keramanizadeh A, Loft S, Møller P. Synergistic effects of zinc oxide nanoparticles and fatty acids on toxicity to caco-2 cells. *Int J Toxicol* 2015; **34**: 67–76.
- 9
10
11
12
13 90 Gu Y, Cheng S, Chen G, Shen Y, Li X, Jiang Q *et al.* The effects of endoplasmic reticulum stress inducer thapsigargin on the toxicity of ZnO or TiO₂ nanoparticles to human endothelial cells. *Toxicol Mech Methods* 2017; **27**: 191–200.
- 14
15
16
17
18 91 Thongkam W, Gerloff K, van Berlo D, Albrecht C, Schins RPF. Oxidant generation, DNA damage and cytotoxicity by a panel of engineered nanomaterials in three different human epithelial cell lines. *Mutagenesis* 2017; **32**: 105–115.
- 19
20
21
22
23 92 Zijno A, Cavallo D, Di Felice G, Ponti J, Barletta B, Butteroni C *et al.* Use of a common European approach for nanomaterials' testing to support regulation: a case study on titanium and silicon dioxide representative nanomaterials. *Journal of Applied Toxicology* 2020; **40**: 1511–1525.
- 24
25
26
27
28 93 Nel AE, Mädler L, Velegol D, Xia T, Hoek EMV, Somasundaran P *et al.* Understanding biophysicochemical interactions at the nano-bio interface. *Nat Mater* 2009; **8**: 543–557.
- 29
30
31
32
33 94 Xia T, Kovoichich M, Liong M, Mädler L, Gilbert B, Shi H *et al.* Comparison of the mechanism of toxicity of zinc oxide and cerium oxide nanoparticles based on dissolution and oxidative stress properties. *ACS Nano* 2008; **2**: 2121–2134.
- 34
35
36
37
38 95 Sauer UG, Vogel S, Aumann A, Hess A, Kolle SN, Ma-Hock L *et al.* Applicability of rat precision-cut lung slices in evaluating nanomaterial cytotoxicity, apoptosis, oxidative stress, and inflammation. *Toxicol Appl Pharmacol* 2014; **276**: 1–20.
- 39
40
41
42
43 96 Srinivas A, Rao PJ, Selvam G, Murthy PB, Reddy PN. Acute inhalation toxicity of cerium oxide nanoparticles in rats. *Toxicol Lett* 2011; **205**: 105–115.
- 44
45
46
47
48 97 Demokritou P, Gass S, Pyrgiotakis G, Cohen JM, Goldsmith W, McKinney W *et al.* An in vivo and in vitro toxicological characterisation of realistic nanoscale CeO₂ inhalation exposures. *Nanotoxicology* 2013; **7**: 1338–1350.
- 49
50
51
52
53 98 Wiemann M, Vennemann A, Sauer UG, Wiench K, Ma-Hock L, Landsiedel R. An in vitro alveolar macrophage assay for predicting the short-term inhalation toxicity of nanomaterials. *J Nanobiotechnology* 2016; **14**: 16.
- 54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 99 Solorio-Rodríguez A, Escamilla-Rivera V, Uribe-Ramírez M, González-Pozos S, Hernández-Soto J, Rafael-Vázquez L *et al.* In vitro cytotoxicity study of superparamagnetic iron oxide and silica nanoparticles on pneumocyte organelles. *Toxicology in Vitro* 2021; **72**: 105071.
- 100 Cavallo D, Ciervo A, Fresegha AM, Maiello R, Tassone P, Buresti G *et al.* Investigation on cobalt-oxide nanoparticles cyto-genotoxicity and inflammatory response in two types of respiratory cells. *Journal of Applied Toxicology* 2015; **35**: 1102–1113.
- 101 Lugun O, Singh J, Singh Thakur R, Pandey AK. Cobalt oxide (Co₃O₄) nanoparticles induced genotoxicity in Chinese hamster lung fibroblast (V79) cells through modulation of reactive oxygen species. *Mutagenesis* 2022; **37**: 44–59.
- 102 Marucco A, Carella E, Fenoglio I. A comparative study on the efficacy of different probes to predict the photo-activity of nano-titanium dioxide toward biomolecules. *RSC Adv* 2015; **5**: 89559–89568.
- 103 Davydov A. *Molecular Spectroscopy of Oxide Catalyst Surfaces*. Wiley, 2003 doi:10.1002/0470867981.
- 104 Collins SE, Briand LE, Gambaro LA, Baltanás MA, Bonivardi AL. Adsorption and Decomposition of Methanol on Gallium Oxide Polymorphs. *The Journal of Physical Chemistry C* 2008; **112**: 14988–15000.
- 105 Bazin P, Thomas S, Marie O, Daturi M. New insights into the methanol oxidation mechanism over Au/CeO₂ catalyst through complementary kinetic and FTIR operando SSITKA approaches. *Catal Today* 2012; **182**: 3–11.
- 106 Bahl A, Hellack B, Wiemann M, Giusti A, Werle K, Haase A *et al.* Nanomaterial categorization by surface reactivity: A case study comparing 35 materials with four different test methods. *NanoImpact* 2020; **19**: 100234.
- 107 Hellack B, Nickel C, Schins RPF. Oxidative potential of silver nanoparticles measured by electron paramagnetic resonance spectroscopy. *Journal of Nanoparticle Research* 2017; **19**: 404.
- 108 Wu Z, Li M, Howe J, Meyer HM, Overbury SH. Probing defect sites on CeO₂ nanocrystals with well-defined surface planes by raman spectroscopy and O₂ adsorption. *Langmuir* 2010; **26**: 16595–16606.
- 109 Pushkarev V V., Kovalchuk VI, D'Itri JL. Probing defect sites on the CeO₂ surface with dioxygen. *Journal of Physical Chemistry B* 2004; **108**: 5341–5348.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 110 Wang Q, Li Y, Serrano-Lotina A, Han W, Portela R, Wang R *et al.* Operando Investigation of Toluene Oxidation over 1D Pt@CeO₂ Derived from Pt Cluster-Containing MOF. *J Am Chem Soc* 2021; **143**: 196–205.
- 111 Wyrwoll AJ, Lautenschläger P, Bach A, Hellack B, Dybowska A, Kuhlbusch TAJ *et al.* Size matters - The phototoxicity of TiO₂ nanomaterials. *Environmental Pollution* 2016; **208**: 859–867.
- 112 Marucco A, Carella E, Fenoglio I. A comparative study on the efficacy of different probes to predict the photo-activity of nano-titanium dioxide toward biomolecules. *RSC Adv* 2015; **5**: 89559–89568.
- 113 Zhang H, Ji Z, Xia T, Meng H, Low-Kam C, Liu R *et al.* Use of Metal Oxide Nanoparticle Band Gap To Develop a Predictive Paradigm for Oxidative Stress and Acute Pulmonary Inflammation. *ACS Nano* 2012; **6**: 4349–4368.
- 114 Arakha M, Roy J, Nayak PS, Mallick B, Jha S. Zinc oxide nanoparticle energy band gap reduction triggers the oxidative stress resulting into autophagy-mediated apoptotic cell death. *Free Radic Biol Med* 2017; **110**: 42–53.
- 115 Paruthi A, Brown JM, Panda E, Gautam ARS, Singh S, Misra SK. Transformation in band energetics of CuO nanoparticles as a function of solubility and its impact on cellular response. *NanoImpact* 2021; **22**. doi:10.1016/j.impact.2021.100324.
- 116 Çetin YA, Martorell B, Serratosa F, Aguilera-Porta N, Calatayud M. Analyzing the TiO₂ surface reactivity based on oxygen vacancies computed by DFT and DFTB methods. *Journal of Physics: Condensed Matter* 2022; **34**: 314004.
- 117 Chou H-H, Ya-Hsuan Liou S, Calatayud M. Modelling rutile TiO₂ nanorod growth preferences: A density functional theory study. *Catal Today* 2020; **356**: 49–55.
- 118 Mancardi G, Mikolajczyk A, Annapoorani VK, Bahl A, Blekos K, Burk J *et al.* A computational view on nanomaterial intrinsic and extrinsic features for nanosafety and sustainability. *Materials Today* 2023; **67**: 344–370.
- 119 Dumit VI, Ammar A, Bakker MI, Bañares MA, Bossa C, Costa A *et al.* From principles to reality. FAIR implementation in the nanosafety community. *Nano Today* 2023; **51**: 101923.
- 120 Moschini E, Gualtieri M, Colombo M, Fascio U, Camatini M, Mantecca P. The modality of cell-particle interactions drives the toxicity of nanosized CuO and TiO₂ in human alveolar epithelial cells. *Toxicol Lett* 2013; **222**: 102–116.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 121 Simeone FC, Costa AL. Assessment of cytotoxicity of metal oxide nanoparticles on the basis of fundamental physical-chemical parameters: A robust approach to grouping. *Environ Sci Nano* 2019; **6**: 3102–3112.
- 122 Reinoso JJ, Rojo MM, del Campo A, Martín-González M, Fernández JF. Highly Efficient Antimicrobial Ceramics Based on Electrically Charged Interfaces. *ACS Appl Mater Interfaces* 2019; **11**: 39254–39262.
- 123 Zuo L, Wijegunawardana D. Redox Role of ROS and Inflammation in Pulmonary Diseases. In: *Advances in Experimental Medicine and Biology*. 2021, pp 187–204.
- 124 Cuillel M, Chevallet M, Charbonnier P, Fauquant C, Pignot-Paintrand I, Arnaud J *et al*. Interference of CuO nanoparticles with metal homeostasis in hepatocytes under sub-toxic conditions. *Nanoscale* 2014; **6**: 1707–1715.
- 125 Mantecca P, Moschini E, Chirico G, Capitani G. Surface bio-interactions stand at the base of the short-term nano CuO-induced cell oxidative stress: insights for a safe(r)-by-design approach. 2022. doi:10.21203/rs.3.rs-1306935/v2.
- 126 Semisch A, Ohle J, Witt B, Hartwig A. Cytotoxicity and genotoxicity of nano - and microparticulate copper oxide: Role of solubility and intracellular bioavailability. *Part Fibre Toxicol* 2014; **11**. doi:10.1186/1743-8977-11-10.
- 127 Strauch BM, Niemand RK, Winkelbeiner NL, Hartwig A. Comparison between micro- and nanosized copper oxide and water soluble copper chloride: Interrelationship between intracellular copper concentrations, oxidative stress and DNA damage response in human lung cells. *Part Fibre Toxicol* 2017; **14**. doi:10.1186/s12989-017-0209-1.
- 128 Diabaté S, Armand L, Murugadoss S, Dilger M, Fritsch-Decker S, Schlager C *et al*. Air–liquid interface exposure of lung epithelial cells to low doses of nanoparticles to assess pulmonary adverse effects. *Nanomaterials* 2021; **11**: 1–23.
- 129 Wu Z, Li M, Mullins DR, Overbury SH. Probing the surface sites of CeO₂ nanocrystals with well-defined surface planes via methanol adsorption and desorption. *ACS Catal* 2012; **2**: 2224–2234.
- 130 Wu Z, Li M, Howe J, Meyer HM, Overbury SH. Probing defect sites on CeO₂ nanocrystals with well-defined surface planes by raman spectroscopy and O₂ adsorption. *Langmuir* 2010; **26**: 16595–16606.
- 131 Trovarelli A. Catalysis by Ceria and Related Materials. 2002; **2**. doi:10.1142/P249.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 132 Tran L, Bañares MA, Rallo R. *Modelling the Toxicity of Nanoparticles*. Springer International Publishing: Cham, 2017 doi:10.1007/978-3-319-47754-1.
- 133 Ziemba M, Schilling C, Ganduglia-Pirovano MV, Hess C. Toward an Atomic-Level Understanding of Ceria-Based Catalysts: When Experiment and Theory Go Hand in Hand. *Acc Chem Res* 2021; **54**: 2884–2893.
- 134 Schilling C, Hofmann A, Hess C, Ganduglia-Pirovano MV. Raman Spectra of Polycrystalline CeO₂: A Density Functional Theory Study. *Journal of Physical Chemistry C* 2017; **121**: 20834–20849.
- 135 Ziemba M, Ganduglia-Pirovano MV, Hess C. Elucidating the Oxygen Storage-Release Dynamics in Ceria Nanorods by Combined Multi-Wavelength Raman Spectroscopy and DFT. *Journal of Physical Chemistry Letters* 2020; **11**: 8554–8559.
- 136 Mittal S, Pandey AK. Cerium Oxide Nanoparticles Induced Toxicity in Human Lung Cells: Role of ROS Mediated DNA Damage and Apoptosis. *Biomed Res Int* 2014; **2014**: 1–14.
- 137 Keller J, Wohlleben W, Ma-Hock L, Strauss V, Gröters S, Küttler K *et al*. Time course of lung retention and toxicity of inhaled particles: short-term exposure to nano-Ceria. *Arch Toxicol* 2014; **88**: 2033–2059.
- 138 Jiang P, Zhang L, Liu X, Ye C, Zhu P, Tan T *et al*. Tuning oxidant and antioxidant activities of ceria by anchoring copper single-site for antibacterial application. *Nature Communications* 2024 15:1 2024; **15**: 1–15.
- 139 Fragou F, Zindrou A, Deligiannakis Y, Louloudi M. Engineering of Oxygen-Deficient Nano-CeO_{2-x} with Tunable Biocidal and Antioxidant Activity. *Cite This: ACS Appl Nano Mater* 2024; **7**: 10552–10564.
- 140 Wang Q, Yeung KL, Bañares MA. Operando Raman-online FTIR investigation of ceria, vanadia/ceria and gold/ceria catalysts for toluene elimination. *J Catal* 2018; **364**: 80–88.
- 141 Wang Q, Li Y, Serrano-Lotina A, Han W, Portela R, Wang R *et al*. Operando Investigation of Toluene Oxidation over 1D Pt@CeO₂ Derived from Pt Cluster-Containing MOF. *J Am Chem Soc* 2021; **143**: 196–205.
- 142 Heckert EG, Seal S, Self WT. Fenton-like reaction catalyzed by the rare earth inner transition metal cerium. *Environ Sci Technol* 2008; **42**: 5014–5019.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- 143 Xue Y, Luan Q, Yang D, Yao X, Zhou K. Direct evidence for hydroxyl radical scavenging activity of cerium oxide nanoparticles. *Journal of Physical Chemistry C* 2011; **115**: 4433–4438.
- 144 Hardas SS, Dan M, Florence RL, Wu P, Grulke EA, Tseng MT *et al.* Rat brain pro-oxidant effects of peripherally administered 5 nm ceria 30 days after exposure. 2012. doi:10.1016/j.neuro.2012.06.007.
- 145 Zhang P, Ma Y, Zhang Z, He X, Zhang J, Guo Z *et al.* Biotransformation of ceria nanoparticles in cucumber plants. *ACS Nano* 2012; **6**: 9943–9950.
- 146 Shi X, Liu Q, Gong Z, Jin Z, Guo H, Wen X *et al.* Vacancy-rich Fe-Ce mixed oxides as nanoenzymes for efficient antioxidant activity in vitro. *Appl Surf Sci* 2024; **664**: 160256.
- 147 Driessen MD, Mues S, Vennemann A, Hellack B, Bannuscher A, Vimalakanthan V *et al.* Proteomic analysis of protein carbonylation: A useful tool to unravel nanoparticle toxicity mechanisms. *Part Fibre Toxicol* 2015; **12**: 1–18.
- 148 Cohen J, Ji Z, Xia T, Demokritou P. An integrated approach for the in vitro dosimetry of engineered nanomaterials : Relevant in vitro dose (RID) functions Background (1 of 2). *Part Fibre Toxicol* 2014; **11**: 1–12.
- 149 Hull M, Kennedy AJ, Detzel C, Vikesland P, Chappell MA. Moving beyond mass: The unmet need to consider dose metrics in environmental nanotoxicology studies. *Environ Sci Technol* 2012; **46**: 10881–10882.
- 150 Fenoglio I, Tomatis M, Lison D, Muller J, Fonseca A, Nagy JB *et al.* Reactivity of carbon nanotubes: Free radical generation or scavenging activity? *Free Radic Biol Med* 2006; **40**: 1227–1233.