

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Dalton Trans.*, 2022, **51**, 14221

Bismuth gallate coordination networks inspired by an active pharmaceutical ingredient†

Erik Svensson Grape,^a Victoria Rooth,^a Simon Smolders,^b Ambre Thiriez,^c Sofia Takki,^a Dirk De Vos,^b Tom Willhammar^a and A. Ken Inge^{*a}

The effect of solvent has been investigated for the synthesis of bismuth gallate compounds, of which the water-based bismuth subgallate has been used as an active pharmaceutical ingredient (API) for over a century. Using methanol as a solvent, two new bismuth gallates were acquired: first a flexible 3-periodic metal–organic framework (MOF) forms, which transforms upon extended synthesis times into a layered 2-periodic coordination polymer of the same bismuth-to-gallate ratio. The structures were determined by three-dimensional electron diffraction. Synthesis in ethanol resulted in the formation of the MOF phase, but not the layered phase. The layered material of the methanol-based synthesis was used as a Lewis acid catalyst due to its higher stability, showing a comparatively quick and regiospecific conversion of styrene oxide to 2-methoxy-2-phenylethanol, indicating the presence of open metal sites in the material. The acquisition of bismuth gallate structures of varying periodicity highlights the prospect of acquiring novel MOFs and coordination polymers from the same components of APIs.

Received 12th July 2022,
Accepted 26th August 2022

DOI: 10.1039/d2dt02260e

rsc.li/dalton

Introduction

Bismuth is often considered to be non-toxic compared to neighbouring elements in the periodic table, and compounds of bismuth containing organic ligands have been used as active pharmaceutical ingredients (APIs) for over a century.¹ Formulations such as bismuth subsalicylate and colloidal bismuth subcitrate (CBS) have mainly been used for their antimicrobial properties, such as in the treatment of *Helicobacter pylori* infections and other gastrointestinal disorders.^{2–6} Recently, bismuth compounds have been shown to efficiently combat antibiotic resistant bacterial strains,⁷ and are gaining interest as catalysts⁸ for their low cost, as well as their non-toxic and non-corrosive nature.⁹ Despite their large-scale production and long history of use, the structures of these materials have largely remained unknown or have only recently been determined. This is due their tendency to form as nanocrystalline powders rather than large single crystals, which can prevent structure determination through conventional means

such as single-crystal X-ray diffraction (SCXRD).^{10,11} Knowledge of a material's structure is fundamental for understanding its physical and chemical properties, which can in turn explain their function and behaviour in biological systems or inspire investigations of previously unexplored properties and applications. For example, the structure of CBS crystallized under acidic conditions was revealed to be a metal–organic framework (MOF),¹² a class of porous materials of interest for applications such as separation and heterogeneous catalysis.^{13,14}

With three-dimensional electron diffraction (3DED), structures of single microcrystals can now be more readily investigated—largely made possible through recent advances in hardware, software, and overall methodology.^{15–19} Using 3DED, bismuth subgallate (BSG), which has been commercially sold as an API since the late 19th century, was revealed by some of us to be a microporous one-dimensional coordination polymer (CP).¹⁰ By finally realizing the structure of BSG, the high stability of the material could be understood, and ideas to investigate previously unexplored sorption properties were conceived. As the structure of a material (*i.e.* the arrangement of molecules/ions and their interactions) can substantially influence its properties, this piqued our interest in altering the structure of this API to develop novel bismuth gallates with varied properties. In BSG, only the phenolate groups of gallate ligands coordinate to Bi³⁺, not the carboxylic acid group, resulting in a 1D structure. It was envisioned that by extending coordination of the gallate linker through both its phenolate and carboxylate groups, 2-periodic or 3-periodic framework structures may

^aDepartment of Materials and Environmental Chemistry, Stockholm University, SE-106 91, Sweden. E-mail: andrew.inge@mmk.su.se^bCentre for Membrane Separations, Adsorption, Catalysis and Spectroscopy for Sustainable Solutions (cMACS), Department of Microbial and Molecular Systems (M2S), KU Leuven, 3001 Leuven, Belgium^cDépartement Sciences et Génie Des Matériaux, INSA, Lyon 69621, France† Electronic supplementary information (ESI) available. CCDC 2183351–2183354. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2dt02260e>

be developed. In addition, the use of gallic acid (also known as 3,4,5-trihydroxybenzoic acid) is of interest for the synthesis of CPs and MOFs as an organic linker that is eco-bio-compatible, sourced from biomass,^{20–25} rather inexpensive and known for its antioxidant properties.

For the synthesis of CPs and MOFs, solvothermal synthesis is the most common approach, providing an opportunity to alter the polarity, acid–base properties, and solubility of the reagents used. In the synthesis of CPs and MOFs, the solvent used can have multiple roles, potentially acting as a reaction medium, structure-directing agent or a ligand coordinating to the metal cation.²⁶ Pertaining to bismuth, it has been shown that the choice of solvent can greatly affect the structure of the acquired product and properties thereof, as was revealed for a series of compounds made from Bi^{3+} and 1,2,4,5-tetrakis-(4-carboxyphenyl)benzene.²⁷ Overall, the formulation, processing, and resulting structure and properties of a material can be greatly influenced by the choice of solvent. Inspecting the recently determined structure of BSG,¹⁰ the presence of a coordinated water molecule that bridges the Bi^{3+} cations within the structure hints at a possibility of acquiring novel phases through syntheses in other solvents.

Results and discussion

In this work, two novel crystalline bismuth gallate phases (1_{MeOH} and **2**) were obtained through solvothermal synthesis in methanol using bismuth nitrate and gallic acid (Fig. 1, see

ESI† for details on the syntheses). After 2 hours of heating, a bismuth gallate MOF (1_{MeOH}), $\text{Bi}(\text{C}_7\text{H}_3\text{O}_5)(\text{MeOH})$, is acquired as plank-shaped crystals (Fig. S1†). Maintaining the same synthesis conditions as 1_{MeOH} but extending the heating time from 2 to 5 hours resulted in a layered phase of the composition, $\text{Bi}(\text{C}_7\text{H}_3\text{O}_5)$, denoted **2**.

The structure of **1** was solved by 3DED (Fig. 2a, b and Table S1†).^{28,29} 1_{MeOH} (Fig. 3a) crystallizes in the polar orthorhombic space group $P2_12_12_1$. The coordination number of bismuth in the structure is 6, with a skewed trapezoidal bipyramidal coordination geometry, and Bi–O bonds ranging from 2.1–2.8 Å, which is a typical range for carboxylate and phenolate interactions with Bi^{3+} cations.^{30,31} The hemidirected coordination environment is characteristic of the stereochemically active lone pair effect common to many Bi^{3+} compounds. Each bismuth cation is coordinated by four bridging phenolate groups and a carboxylate group from surrounding gallates, as well as a methanol molecule, resulting in a rod-shaped inorganic building unit (IBU, Fig. 3b). Each gallate linker coordinates to Bi^{3+} cations through two of the phenolate oxygen atoms in the 3- and 4-positions, as well as through one of the carboxylate oxygen atoms in a monodentate manner. This stands in contrast to the structure of BSG, where all three phenolate groups of the gallate anion coordinate to Bi^{3+} cations but not the carboxylic acid. As the gallates in 1_{MeOH} coordinate on both ends of the molecule, this allows the linker to bridge IBUs into a 3-periodic framework structure, unlike the isolated rod IBUs found in BSG. Phase purity was assessed through a Pawley fit against X-ray powder diffraction (PXRD)

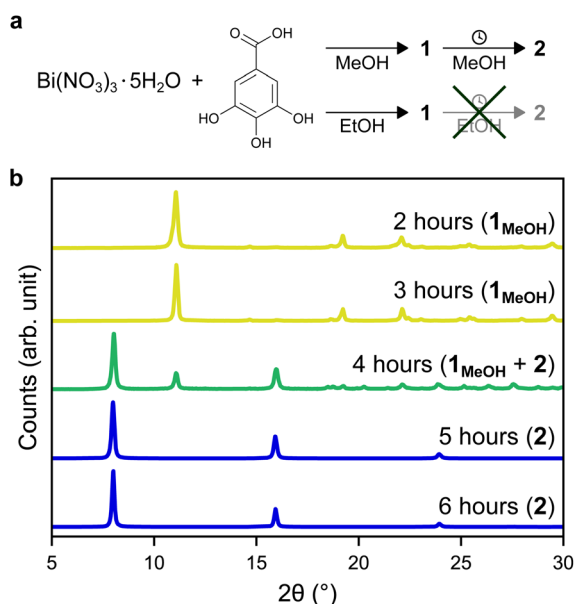


Fig. 1 (a) Schematic representation of the synthesis of $1_{\text{MeOH}}/1_{\text{EtOH}}$ from $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ and gallic acid in methanol/ethanol, where 1_{MeOH} transforms into **2** upon continued heating in methanol. (b) X-ray powder diffraction patterns of bismuth gallates synthesized in methanol under identical conditions apart from different synthesis times. At short reaction times the MOF 1_{MeOH} forms, which after a synthesis time of 4 hours begins to convert into the layered phase, **2**.

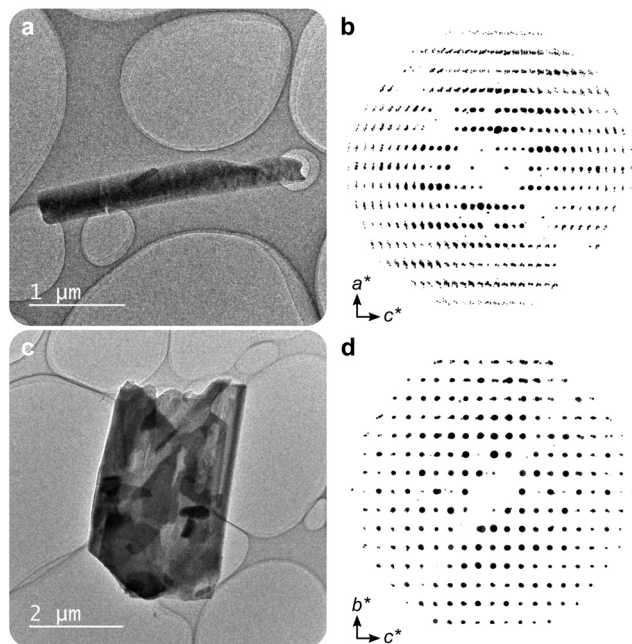


Fig. 2 (a) A crystal of 1_{MeOH} and (b) reconstructed reciprocal lattice based on the acquired 3DED data projected along b^* . (c) A crystal of **2** and (d) reconstructed reciprocal lattice based on the 3DED data projected along a^* .



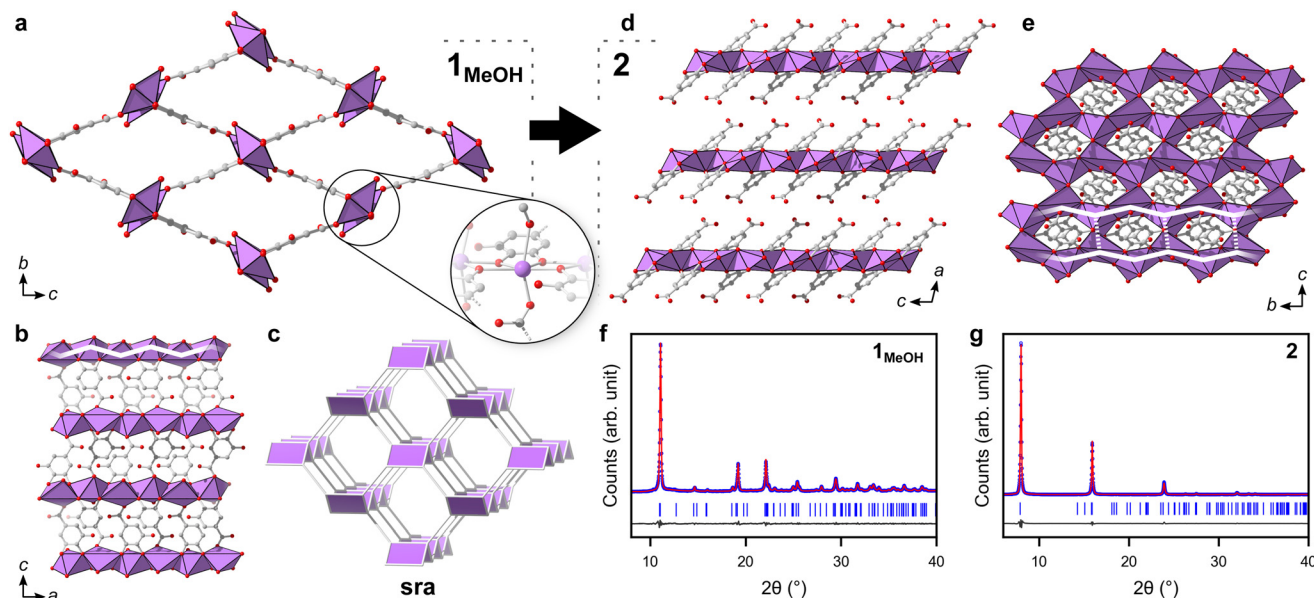


Fig. 3 (a) The structure of 1_{MeOH} as viewed along *a*. Bismuth, oxygen and carbon atoms are coloured purple, red and grey respectively. The methyl group of the coordinated methanol which points into the pores has been omitted for clarity. The insert shows the hemidirected coordination environment around the Bi^{3+} found in the structure. (b) The structure of 1_{MeOH} as viewed along *b*. The partial overlay of a white line over the top row of Bi^{3+} cations shows the zig-zag shape of the inorganic building unit. (c) The underlying **sra** net of **1**. (d) Structure of the layered phase **2** as viewed along *b*. (e) The structure of **2** as viewed along *a*, showing the honeycomb arrangement of bismuth cations. The partial overlay of white lines illustrates the relation to the IBU of **1** where the zig-zag chains are linked into a **hcb** net. (f and g) Difference plots for the Pawley fits of (f) 1_{MeOH} and (g) **2**, respectively, showing that the materials are acquired as pure phases.

data (Fig. 3f, S2 and Table S2†) and the suggested framework composition is further supported by thermogravimetric analysis (TGA), indicating a final sum formula of $\text{Bi}(\text{C}_7\text{H}_3\text{O}_5)(\text{MeOH})\cdot\text{MeOH}$, *i.e.* for every Bi^{3+} cation there is one coordinated methanol and one disordered methanol molecule occupying the void space in the porous structure (Fig. S6†).

Upon inspecting the crystal structure of 1_{MeOH} and assessing the collected FT-IR data (Fig. S9†), the coordinating carboxylate group within the structure is evidently deprotonated as indicated by the lack of the $\text{C}=\text{O}$ stretch band characteristic to carboxylic acids, typically found at 1690 cm^{-1} in the IR spectrum. This results in a charge-balanced material where the third phenolic oxygen on the 5-position of the gallate anion, which does not coordinate to the bismuth cations, remains protonated.

The 3-periodic structure of 1_{MeOH} can be deconstructed into an underlying **sra** net (Fig. 3c), the same as that of the archetypical flexible MOF MIL-53.³² Similarly to MIL-53, it was observed that 1_{MeOH} is also highly flexible upon desorption/heating. The powder diffraction pattern of 1_{MeOH} undergoes noticeable changes in peak positions upon exposing the sample to vacuum or slightly elevated temperatures as a result of the framework flexibility (Fig. S10†), a behaviour which will be discussed for the ethanol analogue, 1_{EtOH} , at the end of this section. As 10.4% of the unit cell volume of 1_{MeOH} is potential solvent-accessible voids, gas sorption experiments were performed. However, the material showed no porosity towards N_2 or CO_2 under the tested experimental conditions, possibly a

consequence of a high energy barrier in re-opening the structure after emptying the framework, which remains crystalline after being exposed to reduced pressures, as was observed from variable temperature PXRD measurements (Fig. S10†). Immersing the solid in water yields the previously characterized BSG (Fig. S13†).¹⁰ Overall, this relatively small number of published metal-gallate structures are of particular interest, as gallic acid and related phenolic compounds are commonly utilized for their chelating abilities and biological roles pertaining to such properties.³³

A second crystalline phase, **2**, which is obtained under similar conditions as 1_{MeOH} but with longer synthesis times (Fig. 1b), forms as plate-shaped crystals and its structure was also solved from 3DED data (Fig. 2c and d). The material crystallizes in the monoclinic space group $P2_1/c$ and analysis of the 3DED data revealed a layered material (Fig. 3d). The coordination number of Bi^{3+} in the structure of **2** is 6 as well, with a hemidirected pentagonal pyramidal coordination geometry involving six bridging phenolates coordinating to each Bi^{3+} cation. The Bi–O distances found within **2** are in good agreement with previously characterized materials, spanning a range of 2.1–2.9 Å. The carboxylic acid group is not involved in coordination and points outwards from the layers. It is protonated, in contrast to what was found for 1_{MeOH} , as validated by FT-IR data (Fig. S9†) by the clear presence of a band at 1690 cm^{-1} which is characteristic of carboxylic acid $\text{C}=\text{O}$ stretching. This preferential coordination of phenolate groups to the metal cation over carboxylate groups is in line with pre-



vious findings in similar materials,^{10,34} such as BSG, owing to the chelation of adjacent phenolate groups of the gallate anions.

The IBUs of **1** and **2** are related (Fig. 4). In **1** the Bi³⁺ coordination environment as aforementioned includes four phenolate, one terminal alcohol and one carboxylate oxygen, and the non-coordinating phenol has a long interatomic distance to the Bi³⁺ cation of 3.3 Å. In **2**, the coordination by the alcohol is lost as well as the carboxylate, and the non-coordinating phenol oxygen in **1** is deprotonated in **2** and coordinates to Bi³⁺ with an interatomic distance of 2.8 Å. In **2** the layered IBU can be simplified into a 2-periodic honeycomb (**hcb**) net (Fig. 3e). This 2-periodic IBU of **2** is related to the zigzagging 1-periodic IBU of **1**_{MeOH} by directly linking the zigzagging IBUs into a layer as illustrated by the white lines in Fig. 3b and e. As such, **2** likely forms as a rearrangement of the **1**_{MeOH} structure: the monodentate carboxylate group coordinated to Bi³⁺ in **1**_{MeOH} detaches and the zig-zag rod-shaped IBUs in **1** are instead joined together *via* the third phenol oxygen of the gallate anions, resulting in the layered IBU found in **2**.

Phase purity of **2** was validated by PXRD (Fig. 1b, S3 and Table S3†) and the suggested formula for the material is Bi(C₇H₃O₅)·MeOH, as was validated from TGA (Fig. S7†), *i.e.* a non-coordinated disordered methanol molecule occupies the void space between layers. Exposing **2** to higher temperatures gives a contraction of the interlayer distance (Fig. S11†), with the unit cell length *a* decreasing from 11.568(3) Å at room temperature in air to 11.390(7) Å at 160 °C, likely due to the removal of inter-layer methanol molecules.

The structure of **2** was shown to have higher thermal stability than **1**, as indicated by variable temperature PXRD (Fig. S11†) and TGA (Fig. S7†), as well as increased stability to moisture, as would be expected based on Ostwald's step rule,

which predicts the tendency of less thermodynamically stable phases to crystallize from solution prior to more stable phases.

Additionally, denser phases typically have higher thermodynamic stability due to their higher density of dispersion forces. The crystal structure of **2** is noticeably denser than **1**_{MeOH} (2.846 vs. 2.254 g cm⁻³, respectively) which is in line with a higher thermodynamic stability of **2** over **1**_{MeOH}. Attempts to synthesize the two materials using ethanol as an alternative solvent to methanol resulted in the acquirement of **1**_{EtOH}. **1**_{EtOH} is a pseudopolymorph of **1**_{MeOH}, as it only differs by the presence of ethanol rather than methanol. However, extending the synthesis time in ethanol did not yield **2** (Fig. 1a), but resulted in the continued presence of **1**_{EtOH}. It is therefore hypothesized that using ethanol as a solvent stabilizes the structure of **1** by better filling the pore space within the material. Exposing as-synthesized **1**_{EtOH} to vacuum (~1 mbar) led to a shrinking of the unit cell by 13%, with unit cell parameters of *a* = 7.540(2) Å, *b* = 8.271(3) Å, *c* = 16.616(4) Å (Fig. S5, S12b and Table S5†). Further, storage of **1**_{EtOH} under ambient conditions for several days yielded a compressed but still crystalline material **1**_{EtOH(stored)}, which, as determined from 3DED measurements (Table S1†) shows a decrease in unit cell volume by 24% (Fig. 5), with unit cell parameters of *a* = 7.73(4) Å, *b* = 6.84(3) Å, *c* = 16.87(8) Å (as synthesized **1**_{EtOH}: *a* = 7.89(4) Å, *b* = 8.61(4) Å, *c* = 17.38(9) Å). The contraction of the structure and narrowing of the pores of **1** occurs through the concerted rotation of the IBUs around the *a*-axis as well as a hinge-like rotation of the coordinated carboxylate groups, resulting in shrinkage of the *b*-axis by 21%. The phase purity of **1**_{EtOH} and unit cell parameters of the partially collapsed

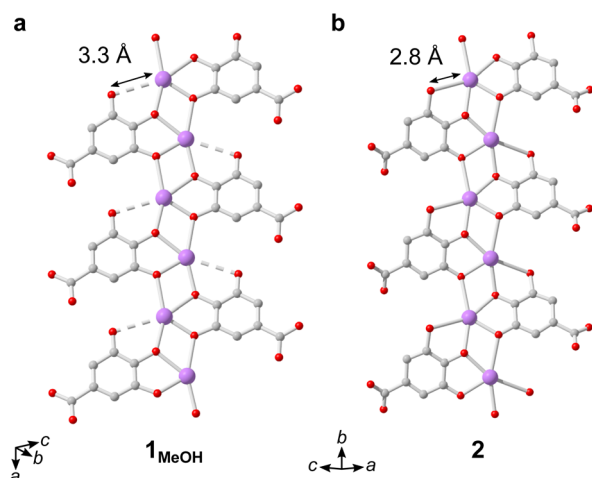


Fig. 4 Select sections of the IBUs of (a) **1**_{MeOH} and (b) **2**, showing similar zig-zag arrangement of Bi³⁺ cations bridged by coordinating phenolate groups. The structures of **1** and **2** thereby mainly differ in the linkage between these IBUs, being joined by carboxylate groups in **1** or phenol groups in **2**. Hydrogen atoms are omitted for clarity.

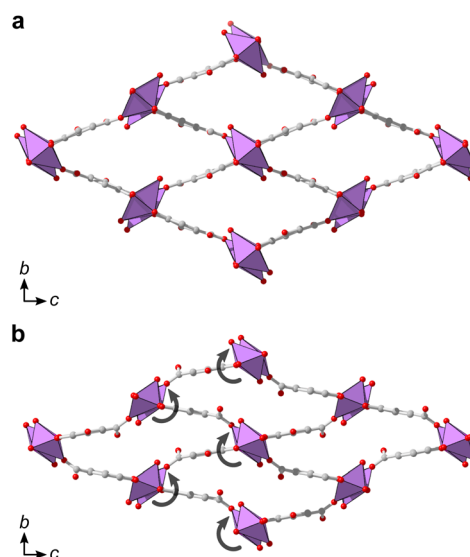


Fig. 5 (a) The structure of as-synthesized **1**_{EtOH} as determined by 3DED viewed along *a* showing a similar pore shape as **1**_{MeOH}. (b) The structure of partially activated **1**_{EtOH(stored)} as viewed along *a*, showing an altered pore shape, resulting in a 24% decrease in unit cell volume (1181(10) Å³ to 891(8) Å³) upon loss of solvent. Semicircular arrows are drawn to illustrate the concerted rotation of the IBUs in the structure. The ethanol carbon atoms and hydrogen atoms are omitted for clarity.



Dalton Trans., 2022, 51, 14221-14227 | 14225

- 19 U. Kolb, Y. Krysiak and S. Plana-Ruiz, *Acta Crystallogr., Sect. B: Struct. Sci., Cryst. Eng. Mater.*, 2019, **75**, 463–474.
- 20 R. Weber and G. Bergerhoff, *Z. Kristallogr. – New Cryst. Struct.*, 1991, **195**, 87–88.
- 21 R. K. Feller and A. K. Cheetham, *Solid State Sci.*, 2006, **8**, 1121–1125.
- 22 P. J. Saines, H. H. M. Yeung, J. R. Hester, A. R. Lennie and A. K. Cheetham, *Dalton Trans.*, 2011, **40**, 6401–6410.
- 23 L. Cooper, T. Hidalgo, M. Gorman, T. Lozano-Fernández, R. Simón-Vázquez, C. Olivier, N. Guillou, C. Serre, C. Martineau, F. Taulelle, D. Damasceno-Borges, G. Maurin, A. González-Fernández, P. Horcajada and T. Devic, *Chem. Commun.*, 2015, **51**, 5848–5851.
- 24 T. Hidalgo, L. Cooper, M. Gorman, T. Lozano-Fernández, R. Simón-Vázquez, G. Mouchaham, J. Marrot, N. Guillou, C. Serre, P. Fertey, Á. González-Fernández, T. Devic and P. Horcajada, *J. Mater. Chem. B*, 2017, **5**, 2813–2822.
- 25 Z. Bao, J. Wang, Z. Zhang, H. Xing, Q. Yang, Y. Yang, H. Wu, R. Krishna, W. Zhou, B. Chen and Q. Ren, *Angew. Chem., Int. Ed.*, 2018, **130**, 16252–16257.
- 26 N. Stock and S. Biswas, *Chem. Rev.*, 2012, **112**, 933–969.
- 27 M. Köppen, V. Meyer, J. Ångström, A. K. Inge and N. Stock, *Cryst. Growth Des.*, 2018, **18**, 4060–4067.
- 28 M. Gemmi, E. Mugnaioli, T. E. Gorelik, U. Kolb, L. Palatinus, P. Boullay, S. Hovmöller and J. P. Abrahams, *ACS Cent. Sci.*, 2019, **5**, 1315–1329.
- 29 Z. Huang, E. Svensson Grape, J. Li, A. K. Inge and X. Zou, *Coord. Chem. Rev.*, 2021, **427**, 213583.
- 30 Q. X. Wang and G. Li, *Inorg. Chem. Front.*, 2021, **8**, 572–589.
- 31 Z. Wang, Z. Zeng, H. Wang, G. Zeng, P. Xu, R. Xiao, D. Huang, S. Chen, Y. He, C. Zhou, M. Cheng and H. Qin, *Coord. Chem. Rev.*, 2021, **439**, 213902.
- 32 C. Serre, F. Millange, C. Thouvenot, M. Noguès, G. Marsolier, D. Louër and G. Férey, *J. Am. Chem. Soc.*, 2002, **124**, 13519–13526.
- 33 B. Badhani, N. Sharma and R. Kakkar, *RSC Adv.*, 2015, **5**, 27540–27557.
- 34 E. Svensson Grape, J. G. Flores, T. Hidalgo, E. Martínez-Ahumada, A. Gutierrez-Alejandre, A. Hautier, D. R. Williams, M. O’Keeffe, L. Öhrström, T. Willhammar, P. Horcajada, I. A. Ibarra and A. Ken Inge, *J. Am. Chem. Soc.*, 2020, **142**, 16795–16804.
- 35 N. Henry, O. Mentré, F. Abraham, E. J. MacLean and P. Roussel, *J. Solid State Chem.*, 2006, **179**, 3087–3094.
- 36 L. Miersch, T. Rüffer, M. Schlesinger, H. Lang and M. Mehring, *Inorg. Chem.*, 2012, **51**, 9376–9384.
- 37 A. K. Inge, M. Köppen, J. Su, M. Feyand, H. Xu, X. Zou, M. O’Keeffe and N. Stock, *J. Am. Chem. Soc.*, 2016, **138**, 1970–1976.
- 38 M. Köppen, A. Dhakshinamoorthy, A. K. Inge, O. Cheung, J. Ångström, P. Mayer and N. Stock, *Eur. J. Inorg. Chem.*, 2018, **2018**, 3496–3503.
- 39 Y. Liu, R. C. Klet, J. T. Hupp and O. Farha, *Chem. Commun.*, 2016, **52**, 7806–7809.
- 40 L. Wang, L. Wang, Y. Du, X. Xu and S. X. Dou, *Mater. Today Phys.*, 2021, **16**, 100294.

