

Cite this: *J. Mater. Chem. A*, 2022, 10, 20048

# Plasmon-enhanced photocatalytic overall water-splitting over Au nanoparticle-decorated $\text{CaNb}_2\text{O}_6$ electrospun nanofibers†

Jiaming Zhang, Xiaoyi Jiang, Jindou Huang, Wei Lu and Zhenyi Zhang \*

The design and construction of wide-bandgap semiconductor nanostructures is a promising way to achieve photocatalytic overall water-splitting, because their redox potentials easily simultaneously satisfy the thermodynamic requirements of water reduction and oxidation. However, the narrow light-harvesting range and the fast charge recombination of wide-bandgap semiconductors tremendously limit their photocatalytic activities. Herein, we developed a novel wide-bandgap semiconductor photocatalyst of  $\text{CaNb}_2\text{O}_6$  nanofibers (NFs) fabricated by an electrospinning technique, followed by calcination. Upon UV-visible light irradiation, the as-electrospun  $\text{CaNb}_2\text{O}_6$  NFs could split water into  $\text{H}_2$  and  $\text{O}_2$  without adding any cocatalyst and sacrificial agent. The  $\text{H}_2$ -production rate of  $\text{CaNb}_2\text{O}_6$  NFs was  $\sim 7.7$  times higher than that of  $\text{CaNb}_2\text{O}_6$  nanoparticles (NPs). It is because the  $\text{CaNb}_2\text{O}_6$  NFs with the NP-packed 1D nanostructure possess abundant homogeneous interfaces to facilitate inter-particle continuous charge migration, thereby prolonging the lifetimes of photoinduced electrons and holes toward both water reduction and oxidation. Notably, the introduction of Au NPs into the  $\text{CaNb}_2\text{O}_6$  NFs could extend light absorption from the UV to the visible light range. The optimal sample of 1.0 at% Au NP-decorated  $\text{CaNb}_2\text{O}_6$  NFs exhibited  $\sim 13.1$ -fold enhancement of photocatalytic activity for overall water splitting as compared to  $\text{CaNb}_2\text{O}_6$  NFs. This remarkable enhancement is attributed to an interesting plasmonic sensitization process, during which the visible-light-excited hot electrons in plasmonic Au NPs are able to transfer to the interband-excited  $\text{CaNb}_2\text{O}_6$  across their hetero-interface for enhancing the photocatalytic water reduction. Meanwhile, the hot holes left in the Au NPs possess a longer lifetime for fulfilling the photocatalytic water oxidation.

Received 4th July 2022  
Accepted 27th July 2022

DOI: 10.1039/d2ta05332b

[rsc.li/materials-a](https://rsc.li/materials-a)

Key Laboratory of New Energy and Rare Earth Resource Utilization of State Ethnic Affairs Commission, Key Laboratory of Photosensitive Materials and Devices of Liaoning Province, School of Physics and Materials Engineering, Dalian Minzu University, 18 Liaohe West Road, Dalian, 116600, P. R. China. E-mail: zhangzy@dlmu.edu.cn

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2ta05332b>



Zhenyi Zhang is a professor in the School of Physics and Materials Engineering at Dalian Minzu University. He received his BS and PhD degrees from Northeast Normal University in 2007 and 2012, respectively. He worked as a postdoctoral research fellow in the Solar Fuels Laboratory at Nanyang Technological University in 2012–2013. His current research interests focus on the design and synthesis of low-

dimensional semiconductor-based photoelectric materials for photocatalysis and sensing applications.

## 1 Introduction

The development of sustainable green energy to replace environmentally hazardous fossil fuels is of great significance to alleviate the prominent global issues of energy shortage and atmospheric contamination.<sup>1–8</sup> Photocatalytic water splitting over highly efficient semiconductor photocatalysts offers a promising approach to convert inexhaustible solar-energy into the non-polluting chemical fuel of  $\text{H}_2$ .<sup>9–18</sup> In theory, wide-bandgap semiconductors are more suitable to be used for photocatalytic overall water splitting as compared to narrow-bandgap semiconductors, because their conduction band (CB) and valence band (VB) positions are easier to straddle the redox potentials of water splitting ( $E_{\text{H}_2/\text{H}_2\text{O}} = 0$  V,  $E_{\text{O}_2/\text{H}_2\text{O}} = +1.23$  V, and pH = 0), thereby thermodynamically favouring the reduction and oxidation of water to  $\text{H}_2$  and  $\text{O}_2$  (Scheme 1A).<sup>19</sup> To date, many wide-bandgap semiconductors, such as  $\text{TiO}_2$ ,  $\text{SrTa}_2\text{O}_6$ , and so on, have been investigated in the research area of photocatalytic water splitting for  $\text{H}_2$  production in the absence of sacrificial agents.<sup>20–23</sup> Among them, columbite niobate compounds ( $\text{ANb}_2\text{O}_6$ ; M = Ba, Sr, Ca, Mg, Ni, etc.) have been considered as one kind of up-and-coming photocatalysts for splitting pure water into  $\text{H}_2$  and  $\text{O}_2$  due to their suitable redox potentials and stable chemical structures.<sup>24–32</sup> It has



Scheme 1 (A) Comparison of redox abilities between narrow- and wide-bandgap semiconductors for the photocatalytic reduction and oxidation of water to  $\text{H}_2$  and  $\text{O}_2$ , respectively; (B) atomic arrangement and structure of columbite  $\text{CaNb}_2\text{O}_6$ .

been reported that upon UV light irradiation,  $\text{CaNb}_2\text{O}_6$  nanoparticles (NPs) are able to reduce pure water to produce  $\text{H}_2$  by virtue of their stronger redox potentials originating from the perovskite-like octahedral structure of  $[\text{NbO}_6]^{7-}$  groups (Scheme 1B).<sup>24,25,27</sup> However, the achievement of broad-spectrum-driven overall pure-water splitting for producing both  $\text{H}_2$  and  $\text{O}_2$  is still a huge challenge for  $\text{CaNb}_2\text{O}_6$  NPs, mainly owing to two drawbacks: (1) the fast recombination of photoinduced charge carriers in  $\text{CaNb}_2\text{O}_6$  NPs tremendously limits the multi-hole-induced water-oxidation for the production of kinetically unfavourable  $\text{O}_2$ ;<sup>33</sup> (2) the large bandgap energy of  $\text{CaNb}_2\text{O}_6$  NPs impedes the absorption and utilization of visible light that comprises approximately 40% of solar irradiation.<sup>34</sup> Thus, it is urgent to seek a rational tactic to synergistically enhance the photoinduced charge separation and visible light absorption of  $\text{CaNb}_2\text{O}_6$  NPs.

In general, single-semiconductor NP-stacked nanostructures can provide abundant homogeneous interfaces to facilitate inter-particle continuous charge migration due to the low lattice mismatch between the NPs.<sup>35</sup> This charge migration process would extend the lifetime of photoinduced charge carriers in semiconductors but without losing their intrinsic redox abilities. Notably, inorganic nanofibers (NFs) made by electrospinning possess a 1D ultra-long porous nanostructure composed of compactly packed NPs.<sup>36</sup> In this context, the electrospinning fabrication of  $\text{CaNb}_2\text{O}_6$  NFs seems to be an effective approach for hindering the charge-carrier recombination and achieving abundant active sites based on the unique 1D nanostructure properties. Importantly, various noble-metal nanostructures with different functional properties could be assembled uniformly in/on inorganic electrospun NFs for further manipulating their light harvesting and charge-carrier kinetic properties.<sup>37,38</sup> For instance, the decoration of plasmonic NPs (Ag, Au, etc.) in/on wide-bandgap-semiconductor electrospun NFs could realize low-photon-energy-driven photocatalytic  $\text{H}_2$ -production based on hot-electron transfer from Au to the contacted semiconductor due to the localized surface plasmon resonance (LSPR) of Au NPs.<sup>39–43</sup> Thus, the introduction of highly stable plasmonic Au NPs into  $\text{CaNb}_2\text{O}_6$  electrospun NFs is a prospective tactic to attain broad-spectrum-driven overall pure water splitting for stoichiometrically producing  $\text{H}_2$  and  $\text{O}_2$ . Nevertheless, the relative exploration has been rarely reported up until now.

In this work, for the first time, we fabricated  $\text{CaNb}_2\text{O}_6$  NFs through calcining electrospun precursor NFs of metal salts/polymer composites at 500, 600, and 700 °C, respectively. The structural characterization results indicate that the as-electrospun  $\text{CaNb}_2\text{O}_6$  NFs with diameters of 60–100 nm were composed of tightly stacked NPs with grain sizes of 3–30 nm, thereby forming lots of homogeneous interfaces among the NPs. These homogeneous interfaces are conducive to prolonging the lifetime of photoinduced charge carriers through inter-particle charge migration, as evidenced by the steady-state and time-resolved photoluminescence (TRPL) spectra and photocurrent testing. Upon UV-visible light irradiation, the  $\text{CaNb}_2\text{O}_6$  NFs could split pure water into  $\text{H}_2$  and  $\text{O}_2$  with the production rates of  $\sim 9.95$  and  $\sim 4.96 \mu\text{mol g}^{-1} \text{h}^{-1}$ , respectively, in the absence of a cocatalyst and sacrificial agent. However, the above stoichiometric water-splitting process could not be realized by using  $\text{CaNb}_2\text{O}_6$  NPs as the photocatalyst (products:  $\text{H}_2$  and  $\text{H}_2\text{O}_2$ ), because the fast recombination of photoinduced electron-hole pairs limits the four-hole-driven water-oxidation reaction.<sup>30</sup> Furthermore, by combining 3D finite-difference-time-domain (FDTD) simulations with wavelength-controlled experiments, we demonstrated an interesting plasmon-enhanced photocatalytic overall water-splitting into  $\text{H}_2$  and  $\text{O}_2$  over the Au NP-decorated  $\text{CaNb}_2\text{O}_6$  NFs. During the photocatalytic process, plasmonic Au NPs could absorb visible light to create energetic hot electrons and holes, which are able to enhance photocatalytic water reduction and oxidation only when the  $\text{CaNb}_2\text{O}_6$  NFs were simultaneously excited to boost the hot electron transfer and reduce the reaction kinetic barrier of multi-hole-driven water oxidation.

## 2 Results and discussion

Based on our proposed fabrication process (Fig. 1A), three  $\text{CaNb}_2\text{O}_6$  samples named  $\text{CaNb}_2\text{O}_6$ -500 NFs,  $\text{CaNb}_2\text{O}_6$ -600 NFs, and  $\text{CaNb}_2\text{O}_6$ -700 NFs were fabricated through an electrospinning technique combined with the subsequent calcination at 500, 600, and 700 °C, respectively. Fig. 1B shows the X-ray diffraction (XRD) patterns of the as-fabricated samples. For the  $\text{CaNb}_2\text{O}_6$ -500 NFs, there is only one broad diffraction band ( $15\text{--}17^\circ$ ) on the XRD pattern, which could be originated from the residual carbon due to the incomplete decomposition of the polymer template at a relative low calcination temperature (Fig. S1†). Meanwhile, the lack of feature diffraction peaks of the  $\text{CaNb}_2\text{O}_6$  crystal may be ascribed to its small grain size and poor crystallinity. Notably, when the calcination temperature was increased during the fabrication process, the feature diffraction peaks of orthorhombic fersmite  $\text{CaNb}_2\text{O}_6$  (JCPDS, no. 11-619) appeared on the XRD patterns of both  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs, suggesting the formation of a  $\text{CaNb}_2\text{O}_6$  phase-structure. Furthermore, according to the Debye–Scherrer formula (Fig. S2†), the average grain sizes of  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs were estimated to be  $\sim 16$  and  $\sim 22$  nm, respectively.

The morphologies and microstructures of the above samples were investigated by using scanning electron microscopy (SEM) and transmission electron microscopy (TEM). As shown in



**Fig. 1** (A) Sketch map of the typical fabrication process of  $\text{CaNb}_2\text{O}_6$  NFs; (B) XRD patterns of (a)  $\text{CaNb}_2\text{O}_6$ -500 NFs, (b)  $\text{CaNb}_2\text{O}_6$ -600 NFs, and (c)  $\text{CaNb}_2\text{O}_6$ -700 NFs; SEM images of (C)  $\text{CaNb}_2\text{O}_6$ -500 NFs, (D)  $\text{CaNb}_2\text{O}_6$ -600 NFs, and (E)  $\text{CaNb}_2\text{O}_6$ -700 NFs; TEM images of the individual (F)  $\text{CaNb}_2\text{O}_6$ -500 NF, (G)  $\text{CaNb}_2\text{O}_6$ -600 NF, and (H)  $\text{CaNb}_2\text{O}_6$ -700 NF; (I–K) HRTEM images from the corresponding yellow-colour squares labelled in images (F–H).

Fig. 1C–E, all these samples have continuous nanofibrous structures with diameters of 60–100 nm and lengths of several micrometres. These NFs are aligned in random orientations and interweaved together. Furthermore, lots of nano-sized pores can be observed on the SEM images of  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs, while there is no distinguishable porous nanostructure on the SEM image of  $\text{CaNb}_2\text{O}_6$ -500 NFs. Further observations from TEM images (Fig. 1F–H) indicate that all the as-fabricated  $\text{CaNb}_2\text{O}_6$  NFs consist of compactly packed NPs with different mean grain sizes ( $\sim 3.5$ ,  $\sim 15.1$  and  $\sim 20.9$  nm) depending on the calcination temperature during the fabrication process (Fig. S2†). During the fabrication process of  $\text{CaNb}_2\text{O}_6$  NFs, the grain size of  $\text{CaNb}_2\text{O}_6$  NPs in the NFs increased with the calcination temperature, thereby leading to larger nanopore sizes in the NFs produced at the higher calcination temperature (Fig. 1C–H and S3†). According to the TEM images in Fig. 1G and H, the mean pore sizes in the  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs are  $\sim 8.9$  and  $\sim 14.3$  nm, respectively (Fig. S2†). Meanwhile, an inter-particle homogeneous interface could be also found in the as-electrospun  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs (Fig. S3†). Fig. 1I–K show the high-resolution (HR) TEM images from the corresponding yellow-colour squares of Fig. 1F–H. As observed in Fig. 1I, the  $\text{CaNb}_2\text{O}_6$ -500 NFs contain lots of small-sized NPs (3–5 nm) with poor crystallinity. However, the selected area electron diffraction (SAED) pattern of the  $\text{CaNb}_2\text{O}_6$ -500 NFs displays the feature diffraction rings of the orthorhombic fersmite  $\text{CaNb}_2\text{O}_6$  (JCPDS, no. 11-619) (Fig. S4†), confirming the formation of polycrystalline  $\text{CaNb}_2\text{O}_6$  NPs in the  $\text{CaNb}_2\text{O}_6$ -500 NFs. Furthermore, lattice fringes with interval distances of  $\sim 0.30$  nm could be observed on the HRTEM images

of  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -700 NFs, respectively, which agrees with the lattice spacing of the (041) plane of orthorhombic fersmite  $\text{CaNb}_2\text{O}_6$ . The above results prove the successful fabrication of  $\text{CaNb}_2\text{O}_6$  NP-stacked 1D NFs by using the electrospinning and calcination methods.

The light absorption properties of the as-fabricated samples were investigated through UV-visible absorption spectra (Fig. 2A). For the  $\text{CaNb}_2\text{O}_6$ -600 NFs, the intrinsic absorption edge is located at  $\sim 350$  nm, which corresponds to the bandgap energy ( $E_g$ ) of  $\text{CaNb}_2\text{O}_6$  at  $\sim 3.54$  eV. In comparison with the  $\text{CaNb}_2\text{O}_6$ -600 NFs, the intrinsic absorption edge of  $\text{CaNb}_2\text{O}_6$ -700 NFs showed a red-shift of  $\sim 25$  nm, indicating a decreased bandgap ( $\sim 3.31$  eV). This red-shift could be attributed to the larger grain-size of  $\text{CaNb}_2\text{O}_6$  NPs in the  $\text{CaNb}_2\text{O}_6$ -700 NFs as compared to that in the  $\text{CaNb}_2\text{O}_6$ -600 NFs. Interestingly, the  $\text{CaNb}_2\text{O}_6$ -500 NFs present broad light absorption ranging from the UV to the visible light region. The visible light absorption is originated from the residual carbon-based impurities in the  $\text{CaNb}_2\text{O}_6$ -500 NFs due to the incomplete decomposition of the PVP template at a relatively low calcination temperature. To estimate the photocatalytic reduction and oxidation abilities of the as-fabricated samples, at first, we performed the half reactions of water splitting for producing  $\text{H}_2$  and  $\text{O}_2$  under UV-



**Fig. 2** (A) UV-visible absorption spectra of the as-fabricated samples; plots of photocatalytic (B)  $\text{H}_2$  and (C)  $\text{O}_2$  yields versus UV-visible light irradiation time over different samples in the presence of  $\text{H}_2\text{C}_2\text{O}_4$  and  $\text{AgNO}_3$  as the hole and electron sacrificial agents, respectively; (D) plots of photocatalytic  $\text{H}_2$  and  $\text{O}_2$  yields versus UV-visible light irradiation time over different samples in pure water without adding any sacrificial agent: (a)  $\text{CaNb}_2\text{O}_6$ -500 NFs; (b)  $\text{CaNb}_2\text{O}_6$ -600 NFs; (c)  $\text{CaNb}_2\text{O}_6$ -700 NFs; (E) the calculated band structures and the DOS curve of  $\text{CaNb}_2\text{O}_6$ ; (F) sketch map of the energy band structure and photocatalytic water-splitting process of  $\text{CaNb}_2\text{O}_6$ -600 NFs for  $\text{H}_2$  and  $\text{O}_2$  production.

visible light irradiation in the presence of oxalic acid ( $\text{H}_2\text{C}_2\text{O}_4$ ) and silver nitrate ( $\text{AgNO}_3$ ) as the hole and electron sacrificial agents, respectively. As shown in Fig. 2B, all the as-fabricated samples can execute photocatalytic water-reduction for producing  $\text{H}_2$  with the rate order of  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $\sim 182.50 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) >  $\text{CaNb}_2\text{O}_6$ -700 NFs ( $\sim 147.50 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) >  $\text{CaNb}_2\text{O}_6$ -500 NFs ( $\sim 50.00 \mu\text{mol g}^{-1} \text{h}^{-1}$ ). Among them, the lowest photocatalytic activity of  $\text{CaNb}_2\text{O}_6$ -500 NFs for  $\text{H}_2$  production is mainly due to their poor crystallization. Meanwhile, the photocatalytic activity of  $\text{CaNb}_2\text{O}_6$ -700 NFs is lower than that of the  $\text{CaNb}_2\text{O}_6$ -600 NFs, which may be attributed to the following reasons: (1) the narrower bandgap of  $\text{CaNb}_2\text{O}_6$ -700 NFs induces a weakened photocatalytic redox ability as compared to the  $\text{CaNb}_2\text{O}_6$ -600 NFs; (2) the smaller sizes of NPs in the  $\text{CaNb}_2\text{O}_6$ -600 NFs may provide more surface active sites for photocatalytic water splitting as compared to that of the  $\text{CaNb}_2\text{O}_6$ -700 NFs; (3) as compared to the  $\text{CaNb}_2\text{O}_6$ -700 NFs, the  $\text{CaNb}_2\text{O}_6$ -600 NFs possess smaller sizes of nanopores, which may cause the formation of more interfaces among the  $\text{CaNb}_2\text{O}_6$ -600 NPs for facilitating the separation of charge carriers. Interestingly, the photocatalytic  $\text{O}_2$ -production rates of the as-fabricated samples also follow the sequence of  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $\sim 22.50 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) >  $\text{CaNb}_2\text{O}_6$ -700 NFs ( $\sim 21.00 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) >  $\text{CaNb}_2\text{O}_6$ -500 NFs ( $\sim 18.00 \mu\text{mol g}^{-1} \text{h}^{-1}$ ), as shown in Fig. 2C. The above results suggest that all the as-fabricated samples are potentially useful for initiating photocatalytic overall water-splitting. And, the  $\text{CaNb}_2\text{O}_6$ -600 NFs possess the strongest photocatalytic redox ability among the as-fabricated three samples. Satisfactorily, when we directly introduced the as-fabricated samples into pure water, both  $\text{H}_2$  and  $\text{O}_2$  with a molar ratio of close to 2 : 1 released after UV-visible light irradiation. The gas production rates of  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $\text{H}_2$ :  $\sim 9.95 \mu\text{mol g}^{-1} \text{h}^{-1}$ ;  $\text{O}_2$ :  $\sim 4.96 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) were higher than those of both  $\text{CaNb}_2\text{O}_6$ -700 NFs ( $\text{H}_2$ :  $\sim 7.18 \mu\text{mol g}^{-1} \text{h}^{-1}$ ;  $\text{O}_2$ :  $\sim 3.58 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) and  $\text{CaNb}_2\text{O}_6$ -500 NFs ( $\text{H}_2$ :  $\sim 4.34 \mu\text{mol g}^{-1} \text{h}^{-1}$ ;  $\text{O}_2$ :  $\sim 2.14 \mu\text{mol g}^{-1} \text{h}^{-1}$ ) (Fig. 2D).

To further confirm the photocatalytic ability of  $\text{CaNb}_2\text{O}_6$  crystals for water splitting, electronic band structures and density of states (DOS) simulations were carried out. As shown in Fig. 2E, the bandgap energy of  $\text{CaNb}_2\text{O}_6$  crystals is simulated to be  $\sim 3.77 \text{ eV}$ , which is similar to the real value of  $\text{CaNb}_2\text{O}_6$ -600 NFs fabricated in our work. Furthermore, the valence band (VB) and conduction band (CB) of  $\text{CaNb}_2\text{O}_6$  crystals are mainly contributed by the O 2p and Nb 4d orbitals, respectively.<sup>44</sup> According to the results of UV-visible absorption spectroscopy and the Mott-Schottky plot (Fig. S5<sup>†</sup>), the VB and CB potentials of the  $\text{CaNb}_2\text{O}_6$ -600 NFs were estimated to be 3.1 V and  $-0.44 \text{ V}$  versus the normal hydrogen electrode (NHE), respectively.<sup>45,46</sup> It can be found that the CB potential of  $\text{CaNb}_2\text{O}_6$ -600 NFs is more negative than  $\text{H}^+/\text{H}_2$  potential (0 V vs. NHE, pH = 0), while its VB potential is more positive than  $\text{O}_2/\text{H}_2\text{O}$  potential (1.23 V vs. NHE, pH = 0) (Fig. 2F). Thus, upon the interband excitation of  $\text{CaNb}_2\text{O}_6$ , the photoinduced electrons and holes on its CB and VB can enable the water reduction and oxidation reactions, respectively, for simultaneously producing  $\text{H}_2$  and  $\text{O}_2$ . However, the  $\text{CaNb}_2\text{O}_6$ -600 NPs made by the sol-gel method with the calcination temperature at  $600 \text{ }^\circ\text{C}$  (Fig. S6<sup>†</sup>) displayed

a dramatic decrease of photocatalytic activity as compared to the  $\text{CaNb}_2\text{O}_6$ -600 NFs for pure water splitting. Upon UV-visible light irradiation, the  $\text{H}_2$  production rate was only  $\sim 1.29 \mu\text{mol g}^{-1} \text{h}^{-1}$ , which was  $\sim 7.7$  times lower than that of the  $\text{CaNb}_2\text{O}_6$ -600 NFs (Fig. 3A). However, the oxidation product of this photocatalytic water-splitting reaction was  $\text{H}_2\text{O}_2$  rather than  $\text{O}_2$  that is a high-kinetically-required product (Fig. S7<sup>†</sup>). The lack of  $\text{O}_2$  products may be attributed to the fast recombination of photoinduced electron-hole pairs in the  $\text{CaNb}_2\text{O}_6$ -600 NFs, thereby hindering the four-hole-driven water-oxidation process. Interestingly, the Brunauer-Emmett-Teller (BET) analysis results indicate that the specific surface area of  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $29.44 \text{ m}^2 \text{ g}^{-1}$ ) was similar to that of the  $\text{CaNb}_2\text{O}_6$ -600 NPs ( $28.84 \text{ m}^2 \text{ g}^{-1}$ ) (Fig. S8<sup>†</sup>). These results suggest that the improved kinetic process of photoinduced charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NFs may play the leading role in increasing the photocatalytic activity for water splitting. To unravel the kinetic process of photoinduced charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NPs and  $\text{CaNb}_2\text{O}_6$ -600 NFs, their steady-state and time-resolved photoluminescence (TRPL) spectra were recorded.<sup>47-49</sup> As shown in Fig. 3B, both  $\text{CaNb}_2\text{O}_6$ -600 NPs and  $\text{CaNb}_2\text{O}_6$ -600 NFs show emission bands centred at  $\sim 467 \text{ nm}$  after 280 nm excitation. Meanwhile, the emission intensity of  $\text{CaNb}_2\text{O}_6$ -600 NFs is lower than that of the  $\text{CaNb}_2\text{O}_6$ -600 NPs, suggesting the suppressed recombination process of photoinduced charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NFs. Fig. 3C displays the TRPL spectra of the above two samples, in which all the emission decay curves can be fitted by the biexponential kinetic function:

$$I(t) = A_1 \cdot \exp(-t/\tau_1) + A_2 \cdot \exp(-t/\tau_2) + B \quad (1)$$

where  $\tau_1$  and  $\tau_2$  are the fluorescence lifetimes, and  $A_1$ , and  $A_2$  are the corresponding amplitudes. In general, the longer lifetime ( $\tau_1$ ) is contributed by the recombination of free charge carriers

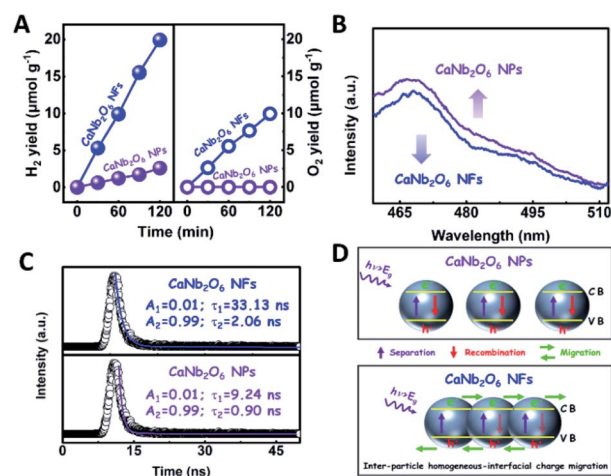


Fig. 3 (A) Plots of photocatalytic  $\text{H}_2$  and  $\text{O}_2$  yields versus UV-visible light irradiation time over the  $\text{CaNb}_2\text{O}_6$  NPs and  $\text{CaNb}_2\text{O}_6$  electrospun NFs in pure water; (B) steady-state PL spectra and (C) time-resolved transient PL decay of  $\text{CaNb}_2\text{O}_6$  NPs and  $\text{CaNb}_2\text{O}_6$  NFs; (D) sketch maps of the kinetic processes of photoinduced charge carriers in the  $\text{CaNb}_2\text{O}_6$  NPs and  $\text{CaNb}_2\text{O}_6$  NFs, respectively.

in a semiconductor, while the shorter lifetime ( $\tau_2$ ) is induced by the nonradiative recombination of charge carriers originating from the surface defect of the semiconductor.<sup>36,43</sup> It can be found that both the  $\tau_1$  and  $\tau_2$  values of  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $\tau_1 = 33.13$  ns;  $\tau_2 = 2.06$  ns) are longer than the corresponding lifetimes of  $\text{CaNb}_2\text{O}_6$ -600 NPs ( $\tau_1 = 9.24$  ns;  $\tau_2 = 0.90$  ns). The quenched PL and the extended fluorescence lifetimes suggest the slower recombination process of charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NFs after the interband excitation. This phenomenon can be ascribed to the different microstructures between the  $\text{CaNb}_2\text{O}_6$ -600 NFs and  $\text{CaNb}_2\text{O}_6$ -600 NPs. As illustrated in Fig. 3D, the number of homogeneous interfaces in the  $\text{CaNb}_2\text{O}_6$ -600 NFs is more than that of the  $\text{CaNb}_2\text{O}_6$ -600 NPs due to the unique 1D nanostructure properties of the electrospun NFs. These homogeneous interfaces could facilitate interparticle continuous charge migration, thereby leading to the longer lifetimes of photoinduced charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NFs as compared to those of the  $\text{CaNb}_2\text{O}_6$ -600 NPs. These long-lived charge carriers in the  $\text{CaNb}_2\text{O}_6$ -600 NFs could accelerate the reaction kinetics of both water reduction and oxidation to enhance the photocatalytic  $\text{H}_2$  and  $\text{O}_2$  production. To further confirm this hypothesis, electrochemical photocurrent tests were carried out on both the  $\text{CaNb}_2\text{O}_6$ -600 NPs and  $\text{CaNb}_2\text{O}_6$ -600 NFs under UV-visible light irradiation with several on-off cycles. As expected, the photocurrent value of the  $\text{CaNb}_2\text{O}_6$ -600 NFs ( $\sim 10.87$  nA) was obviously higher than that of the  $\text{CaNb}_2\text{O}_6$ -600 NPs ( $\sim 5.07$  nA) (Fig. S9†).

In order to further extend the light absorption range and improve the charge-carrier kinetic process of the optimal  $\text{CaNb}_2\text{O}_6$ -600 NFs, the different contents of plasmonic Au NPs (atomic ratio of Au to Ca: 0.25, 0.5, 0.75, 1.0, and 1.25 at%) were introduced into the  $\text{CaNb}_2\text{O}_6$ -600 NFs by using the electrospinning and calcination methods. It is expected that the plasmonic Au NPs absorb and utilize visible light to further enhance the photocatalytic water-splitting activity (Fig. 4A). As shown in Fig. 4B, the diffraction peaks of all the as-fabricated  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs ( $x = 0.25, 0.5, 0.75, 1.0,$  and  $1.25$ ) can be perfectly indexed to orthorhombic fersmite  $\text{CaNb}_2\text{O}_6$  (JCPDS, no. 11-619), indicating the unchanged phase structure of  $\text{CaNb}_2\text{O}_6$  NFs after the introduction of Au NPs. However, the characteristic diffraction peaks of Au NPs were not observed on the XRD patterns of the as-fabricated  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs. This phenomenon may be attributed to the low content and small sizes of Au NPs in the  $\text{CaNb}_2\text{O}_6$  nanofibrous matrix, thereby leading to weak crystal-diffraction signals beyond the XRD probing limit. Furthermore, all the  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs maintain the 1D porous nanofiber structures. Their structural parameters (several micrometres in lengths and 60–100 nm in diameters) are similar to those of the pristine  $\text{CaNb}_2\text{O}_6$  NFs (Fig. 4C, D and S10†). Fig. 4D shows the dark-field scanning TEM (STEM) image and the corresponding element-mapping images of the  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs. The element-mapping images show that the Ca, Nb, Au, and O elements co-exist in the  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs. However, the Au and Nb elements in the NFs cannot be distinguished by the TEM-element mapping due to their similar Energy-Dispersive X-ray Spectroscopy (EDS) spectra (Fig. S11A†). Nevertheless, the bright Au NPs can be still found on the dark-

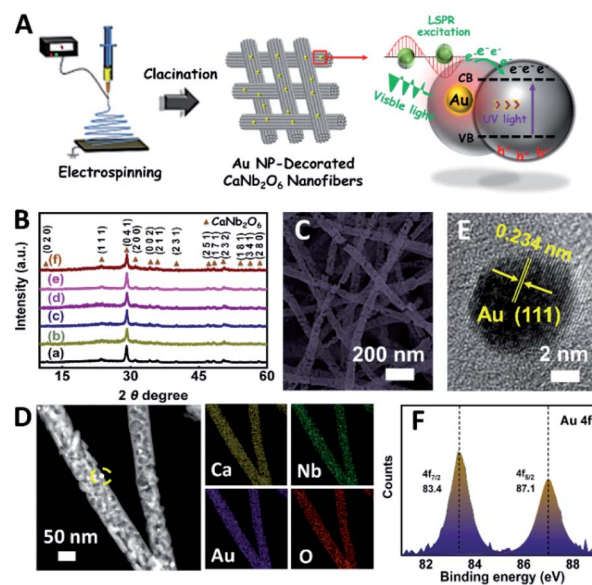
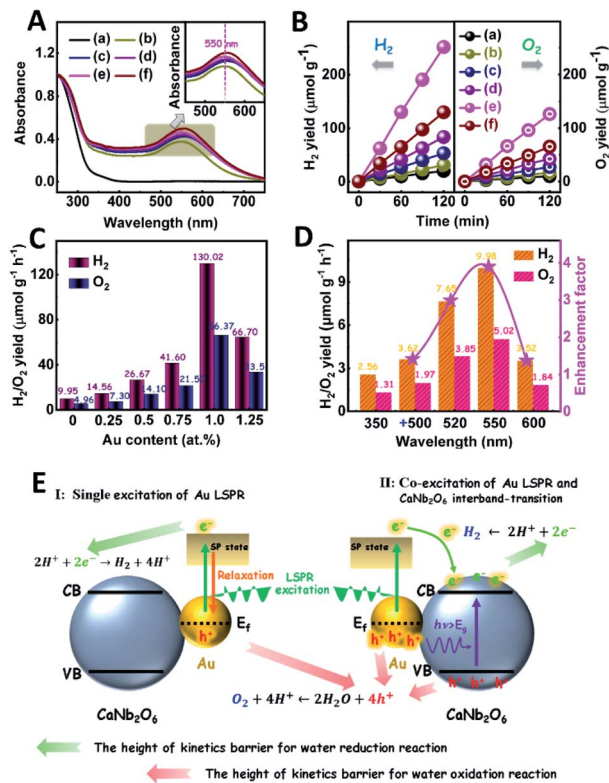


Fig. 4 (A) Sketch map showing the typical fabrication process of the Au NP-decorated  $\text{CaNb}_2\text{O}_6$  NFs; (B) XRD patterns of (a)  $\text{CaNb}_2\text{O}_6$ -600 NFs, (b)  $\text{Au}_{0.25}/\text{CaNb}_2\text{O}_6$  NFs, (c)  $\text{Au}_{0.5}/\text{CaNb}_2\text{O}_6$  NFs, (d)  $\text{Au}_{0.75}/\text{CaNb}_2\text{O}_6$  NFs, (e)  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs and (f)  $\text{Au}_{1.25}/\text{CaNb}_2\text{O}_6$  NFs; (C) SEM image of  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs; (D) dark-field STEM and the corresponding elemental mapping images of  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs; (E) HRTEM image from the yellow-coloured square of Fig. 4D; (F) XPS spectrum: Au 4f core level for the  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs.

field STEM of  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs (Fig. S11B†). Further investigation by using the TEM image indicates that the Au NPs with a mean size of  $\sim 10.03$  nm were dispersed randomly on/in the  $\text{CaNb}_2\text{O}_6$  electrospun NFs (Fig. S12†). Fig. 4E shows the HRTEM image of the spherical NP selected from the yellow colour square of Fig. 4D. The interplanar distance of  $\sim 0.234$  nm corresponds well to the lattice spacing of the Au (111) plane. The formation of metallic Au can be also confirmed by X-ray photoelectron spectroscopy (XPS). As observed in Fig. 4F, the Au  $4f_{7/2}$  and Au  $4f_{5/2}$  peaks of  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs are positioned at 83.4 and 87.1 eV, respectively, which are in accordance with the corresponding values of the metallic  $\text{Au}^0$  state.<sup>50</sup> Meanwhile, the valence states of Ca and Nb ions in both the  $\text{CaNb}_2\text{O}_6$  and  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs are +2 and +5, respectively (Fig. S13†).

The light absorption properties of the as-fabricated  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs were investigated in comparison with those of the  $\text{CaNb}_2\text{O}_6$ -600 NFs through UV-visible absorption spectra. As shown in Fig. 5A, the intense UV-light absorption of all the as-fabricated samples can be assigned to the intrinsic absorption of  $\text{CaNb}_2\text{O}_6$ . Compared to the  $\text{CaNb}_2\text{O}_6$ -600 NFs, all the  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs exhibited obvious visible-light absorption bands at  $\sim 550$  nm (the inset of Fig. 5A). These absorption bands are attributed to the LSPR of Au NPs in the  $\text{CaNb}_2\text{O}_6$  NFs.<sup>51</sup> The similar position ( $\sim 550$  nm) of plasmonic absorption bands suggests that the sizes of Au NPs were almost unchanged in the as-fabricated  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs.

The photocatalytic activities of the as-fabricated  $\text{Au}_x/\text{CaNb}_2\text{O}_6$  NFs for overall water splitting were evaluated under UV-visible light irradiation in the absence of any sacrificial



**Fig. 5** (A) UV-visible absorption spectra of the as-fabricated samples; (B) plots of photocatalytic H<sub>2</sub> and O<sub>2</sub> yields versus UV-visible light irradiation time over different samples in pure water without adding any sacrificial agent: (a) CaNb<sub>2</sub>O<sub>6</sub>-600 NFs, (b) Au<sub>0.25</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, (c) Au<sub>0.5</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, (d) Au<sub>0.75</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, (e) Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs and (f) Au<sub>1.25</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs; (C) photocatalytic H<sub>2</sub> and O<sub>2</sub> production rates over Au/CaNb<sub>2</sub>O<sub>6</sub> NFs with different Au contents under UV-visible light irradiation; (D) photocatalytic H<sub>2</sub> and O<sub>2</sub> yield rates over Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs under 350 nm irradiation in the absence or presence of secondary beam irradiation with the wavelength at 500 ± 15, 520 ± 15, 550 ± 15, and 600 ± 15 nm, respectively; (E) schematic diagram showing the plasmon-mediated photocatalytic overall water splitting over Au/CaNb<sub>2</sub>O<sub>6</sub> NFs after the single excitation of Au LSPR or the co-excitation of Au LSPR and CaNb<sub>2</sub>O<sub>6</sub> interband-transition.

agent. The control experiment results indicate that no H<sub>2</sub> and O<sub>2</sub> were detected in the absence of either the as-fabricated NFs or the light irradiation. As shown in Fig. 5B, all the Au<sub>x</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs exhibit enhanced photocatalytic activities for overall water splitting as compared to the pure CaNb<sub>2</sub>O<sub>6</sub> NFs (H<sub>2</sub>: ~9.95 μmol g<sup>-1</sup> h<sup>-1</sup>; O<sub>2</sub>: ~4.96 μmol g<sup>-1</sup> h<sup>-1</sup>). The enhanced photocatalytic activity of Au<sub>x</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs may be attributed to the LSPR of Au NPs that can induce hot-electron transfer from the Au to CaNb<sub>2</sub>O<sub>6</sub> components. Please note that the LSPR absorption of Au NPs is unmatched with the light absorption of CaNb<sub>2</sub>O<sub>6</sub> NFs, and therefore no plasmon resonance energy transfer process occurs in the Au<sub>x</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs. Notably, the optimal sample of Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs possesses the H<sub>2</sub> and O<sub>2</sub> production rates of ~130.02 and ~66.37 μmol g<sup>-1</sup> h<sup>-1</sup>, respectively (Fig. 5C). These gas-production rates are about 13.1 times higher than the corresponding rates of the CaNb<sub>2</sub>O<sub>6</sub>-600 NFs. However, when the content of Au NPs was higher than 1.0 at%, the photocatalytic activity of Au NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs was decreased

(Fig. 5C). This can be ascribed to the “shield effect” of Au NPs to reduce the light absorption and active sites of the CaNb<sub>2</sub>O<sub>6</sub> NFs.

To further recognize the contribution of Au LSPR to the photocatalytic activity of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, we performed photocatalytic overall water-splitting upon dual-beam irradiation with different photon energies, in which one beam was for the CaNb<sub>2</sub>O<sub>6</sub> interband excitation (350 nm), and the other was for Au LSPR excitation (500–600 nm). Upon single irradiation at 350 nm, the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs are able to split pure water into H<sub>2</sub> and O<sub>2</sub> with the production rates of ~2.56 and ~1.31 μmol g<sup>-1</sup> h<sup>-1</sup>, respectively (Fig. 5D). However, there was no detectable gas release over the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, when we adjusted the single irradiation wavelength at 500 ± 15, 520 ± 15, 550 ± 15 and 600 ± 15 nm, respectively, to only excite the Au LSPR. Please note that the above excitation wavelength (500–600 nm) is selected according to the UV-visible absorption spectrum of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (Fig. 5A). These results suggest that the plasmon-induced hot electrons and holes over Au NPs cannot directly initiate the photocatalytic reaction of pure water splitting, because the ultra-fast relaxation of plasmonic hot-excitons in Au NPs cannot satisfy the reaction kinetic requirements of water oxidation and reduction for producing O<sub>2</sub> and H<sub>2</sub>. Interestingly, when the above dual-beam irradiation was simultaneously used to execute the photocatalytic water splitting, the H<sub>2</sub> and O<sub>2</sub> production rates of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs could be obviously enhanced as compared to the corresponding rates obtained upon single irradiation at 350 ± 15 nm (Fig. 5D). Furthermore, the enhancement factors, obtaining from the ratio values of the H<sub>2</sub>-production rates of Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs under dual-beam irradiation to the H<sub>2</sub>-production rate of Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs under the single irradiation at 350 ± 15 nm, were basically correlated with the plasmonic absorption band of Au NPs in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (Fig. S14<sup>†</sup>). These observations indicate that the LSPR-induced hot electrons and holes over Au NPs could enhance the photocatalytic activity of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs for water splitting only when the CaNb<sub>2</sub>O<sub>6</sub> component was simultaneously excited to boost the hot electron transfer and unlock reaction kinetic barrier. The introduction of plasmonic Au NPs into the CaNb<sub>2</sub>O<sub>6</sub> NFs can extend the light absorption and utilization range from the UV to the visible light region, thereby realizing the UV-visible-light-driven photocatalytic overall water splitting over the Au/CaNb<sub>2</sub>O<sub>6</sub> NFs (Fig. S15<sup>†</sup>). According to the above results, the single excitation of Au-LSPR in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs could not directly initiate photocatalytic overall water splitting for producing H<sub>2</sub> and O<sub>2</sub> in the absence of a sacrificial agent. This may be due to the fast relaxation of plasmonic hot electrons and the high kinetic requirement of water oxidation to O<sub>2</sub> (four-hole reaction) (Fig. 5E). Interestingly, semiconductors of such CaNb<sub>2</sub>O<sub>6</sub> possess high conductivity after interband excitation,<sup>49</sup> which could boost the hot electron transfer in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs. Meanwhile, the transfer process of hot electrons in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs could also prolong the lifetime of plasmon-induced hot holes in the Au NPs, thereby promoting the hot-hole transfer from Au to H<sub>2</sub>O for reducing the kinetic reaction barrier of water oxidation to O<sub>2</sub> (Fig. 5E). Thus, the plasmon-induced hot electron transfer process in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs

could extend the lifetimes of plasmonic hot excitons for enhancing the photocatalytic activity of overall water splitting.

The plasmon-induced electron transfer process in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs can be deduced based on the Bode phase plots through the following equation:<sup>52</sup>

$$\tau_n = \frac{1}{2\pi f_{\max}} \quad (2)$$

As observed in Fig. S16,<sup>†</sup> upon single irradiation at 350 nm, the  $f_{\max}$  value of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs is  $\sim 13.11$  Hz. Interestingly, when we employed dual-beam irradiation with two wavelengths at  $350 \pm 15$  and  $550 \pm 15$  nm to simultaneously excite the CaNb<sub>2</sub>O<sub>6</sub> interband transition and the Au LSPR, its  $f_{\max}$  value could reduce to  $\sim 5.81$  Hz. Therefore, it can be calculated that the electron lifetime of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs ( $\sim 27.3$  ms) obtained under dual-beam irradiation was about 2.2 times longer than that obtained under single beam irradiation ( $\sim 12.1$  ms). The longer electron lifetime means that the co-excitation of Au LSPR and CaNb<sub>2</sub>O<sub>6</sub> interband transition could effectively extend the electron transfer process due to the hot electron transfer from Au NPs to the contacted CaNb<sub>2</sub>O<sub>6</sub> NFs. As a result, upon dual-beam irradiation (350 nm + 550 nm), more available electrons and holes could be accumulated on the CaNb<sub>2</sub>O<sub>6</sub> and Au components for fulfilling the photocatalytic splitting of pure water into H<sub>2</sub> and O<sub>2</sub>, respectively.

As we know, the LSPR-induced localized electric-field enhancement behavior is important for the generation of hot electrons in plasmonic nanostructures.<sup>53</sup> In general, the large enhancement of the electric-field intensity would boost the generation of hot electrons in plasmonic nanostructures.<sup>54–56</sup> Thus, to further reveal the LSPR-induced hot electron generation in the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, 3D finite-difference time domain (FDTD) simulations were carried out. According to the TEM images of Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (bottom images of Fig. 6B–D), we simplified the simulation model as the individual Au/CaNb<sub>2</sub>O<sub>6</sub> NF, in which Au NPs were assembled in the CaNb<sub>2</sub>O<sub>6</sub> NF with three typical positions (Fig. 6A). The LSPR excitation of Au NPs at 550 nm can remarkably enhance the localized electric-field intensities ( $|E|^2/|E_0|^2$ ) in the near surface regions of Au NPs in the Au/CaNb<sub>2</sub>O<sub>6</sub> NF (Fig. 6B–D top images). Moreover, the enhancement of the electric-field intensity depends on the position of Au NPs in/on the CaNb<sub>2</sub>O<sub>6</sub> NF. When the Au NP was

positioned on the outer surface of CaNb<sub>2</sub>O<sub>6</sub> NF, the LSPR-enhanced electric-field intensity could reach  $\sim 36\times$  in the Au/CaNb<sub>2</sub>O<sub>6</sub> interface region. However, the embedment of Au NPs in the middle and near-surface of the CaNb<sub>2</sub>O<sub>6</sub> NF could induce  $\sim 4$ -fold and  $\sim 9$ -fold enhancements of the electric-field intensities, respectively. The above simulation results indicate that the Au/CaNb<sub>2</sub>O<sub>6</sub> interface can strongly concentrate the incident visible light to generate lots of hot electrons at the surface plasmon (SP) states of Au NPs. These hot electrons further transfer from Au NPs to the excited CaNb<sub>2</sub>O<sub>6</sub> for enhancing the photocatalytic water-reduction activity of the CaNb<sub>2</sub>O<sub>6</sub> NFs, while the hot holes left in Au NPs possess extended lifetimes for initiating the photocatalytic water oxidation. The above results and analyses suggest that when the Au/CaNb<sub>2</sub>O<sub>6</sub> NFs encounter UV-visible light irradiation, the LSPR-induced hot electrons would move to the CaNb<sub>2</sub>O<sub>6</sub> surface for reducing water to H<sub>2</sub>, while the hot holes stay on the Au surface for oxidizing water to O<sub>2</sub>. It also means that in the Au/CaNb<sub>2</sub>O<sub>6</sub> interface region, the active sites for water reduction and oxidation are mainly positioned at the surface of the CaNb<sub>2</sub>O<sub>6</sub> and Au components, respectively.

To consolidate the above conclusion, the energy barrier to break the O–H bond of H<sub>2</sub>O on CaNb<sub>2</sub>O<sub>6</sub> and Au/CaNb<sub>2</sub>O<sub>6</sub> was calculated by nudged elastic band (NEB) calculations, respectively. As observed in Fig. 7A and B, the length of the O–H bond of the water molecule adsorbed on the CaNb<sub>2</sub>O<sub>6</sub> surface is 1.107 Å, which is smaller than that at the Au/CaNb<sub>2</sub>O<sub>6</sub> interface (1.357 Å), but is larger than that of the normal water molecule (0.99 Å). Meanwhile, the adsorption energy of H<sub>2</sub>O at the Au/CaNb<sub>2</sub>O<sub>6</sub> interface is about 1.3 eV (Fig. S17A<sup>†</sup>), and the distance between the O atom of H<sub>2</sub>O and the adjacent Au atom is about 2.153 Å. It indicates that H<sub>2</sub>O can be a chemically bonded moiety on the Au surface. In comparison, the adsorption energy for H<sub>2</sub>O on the CaNb<sub>2</sub>O<sub>6</sub> surface is about 0.69 eV (Fig. S17B<sup>†</sup>). This weaker interaction may decrease the activation effect on H<sub>2</sub>O on the CaNb<sub>2</sub>O<sub>6</sub> surface. Thus, the hydrolytic energy barrier can be substantially reduced by the introduction of Au NPs into the CaNb<sub>2</sub>O<sub>6</sub> NFs. Accordingly, the energy barrier for the reaction H<sub>2</sub>O\*  $\rightarrow$  OH\* + H\* occurring at the Au/CaNb<sub>2</sub>O<sub>6</sub> interface ( $E_a = 0.14$  eV) is much lower than the one for H<sub>2</sub>O\*  $\rightarrow$  OH\* + H\* on the CaNb<sub>2</sub>O<sub>6</sub> surface ( $E_a = 0.47$  eV) (Fig. 7A and B). The above results suggest that the Au/CaNb<sub>2</sub>O<sub>6</sub> interface is beneficial to dissociate the water molecule due to the strong interactions between the O atom of H<sub>2</sub>O and the Au atom. Notably, in the final state (FS) of the H<sub>2</sub>O-adsorbed Au/CaNb<sub>2</sub>O<sub>6</sub> interface (Fig. 7B), the O atom of H<sub>2</sub>O is bonded with Au, while the H atom of H<sub>2</sub>O is linked with CaNb<sub>2</sub>O<sub>6</sub>. This kind of chemical structure implies that for the Au/CaNb<sub>2</sub>O<sub>6</sub> NFs the Au component serves as the active site for the photocatalytic O<sub>2</sub> production, while the CaNb<sub>2</sub>O<sub>6</sub> component acts as the active site for the H<sub>2</sub> production. This result is consistent with our proposed mechanism of plasmon-enhanced photocatalytic overall water splitting.

To further assess the photocatalytic activity of the optimal Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs, 1.0 at% Pt NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs were fabricated as the control sample (Fig. S18 and S19<sup>†</sup>). It is well known that Pt is a commonly used cocatalyst and possesses the

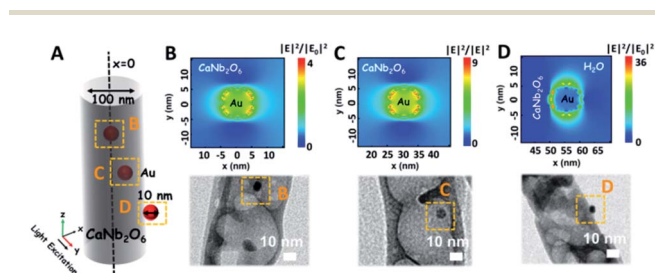


Fig. 6 (A) Simplified structural model of the Au/CaNb<sub>2</sub>O<sub>6</sub> NFs for the FDTD simulation; (B–D) simulated electric-field distributions and the corresponding TEM images of Au/CaNb<sub>2</sub>O<sub>6</sub> NFs with the Au NP position at B, C, and D yellow squares of (A).

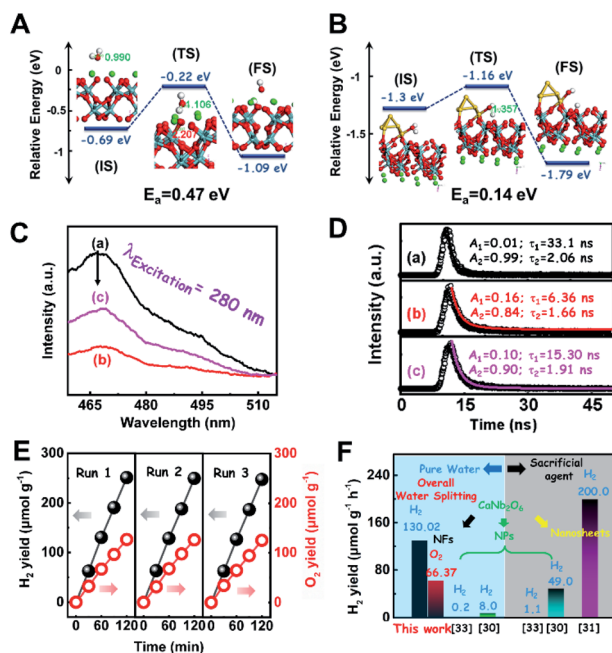


Fig. 7 NEB calculations of the H<sub>2</sub>O decomposition processes on the (A) CaNb<sub>2</sub>O<sub>6</sub> and (B) Au/CaNb<sub>2</sub>O<sub>6</sub> surfaces (IS: initial state; TS: transition state; FS: final state); (C) steady-state PL spectra and (D) time-resolved transient PL decay of the as-fabricated samples: (a) CaNb<sub>2</sub>O<sub>6</sub>-600 NFs; (b) Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs; (c) Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs; (E) cycling test of photocatalytic overall water splitting for the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> composite NFs; (F) comparison of the photocatalytic activity of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs for water splitting with that of CaNb<sub>2</sub>O<sub>6</sub>-based photocatalysts reported in the literature.

excellent “electron sink” effect and low overpotential for H<sub>2</sub> production.<sup>51–53</sup> However, to our surprise, the photocatalytic activity of Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs for H<sub>2</sub> and O<sub>2</sub> production (~37.50 and ~19.00 μmol g<sup>-1</sup> h<sup>-1</sup>) was much lower than that of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (~130.02 and ~66.37 μmol g<sup>-1</sup> h<sup>-1</sup>) upon UV-visible light irradiation. This result indicates that in comparison with the “electron sink” effect of Pt NPs, the LSPR of Au NPs is a more effective for enhancing the photocatalytic activity of CaNb<sub>2</sub>O<sub>6</sub> NFs for water splitting.

To clarify the “electron sink” effect of metal NPs (Au and Pt) on the enhancement of photocatalytic activity for water splitting, the steady-state PL spectroscopy spectra of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> and Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs were tested in comparison with that of the pure CaNb<sub>2</sub>O<sub>6</sub> NFs. As observed in Fig. 7C, the CaNb<sub>2</sub>O<sub>6</sub> NFs present an intense emission band with the peak at ~467 nm after UV light irradiation at 280 nm. However, the introduction of noble-metal NPs into CaNb<sub>2</sub>O<sub>6</sub> NFs could obviously decrease the PL intensity of CaNb<sub>2</sub>O<sub>6</sub> NFs. Meanwhile, the PL intensity of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs is lower than that of CaNb<sub>2</sub>O<sub>6</sub> NFs, but is higher than that of the Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs. The reduced PL intensity reveals either a faster transfer process with a shorter lifetime or a slower recombination process with a longer lifetime of the photoinduced electrons.<sup>57</sup> To further understand the reason for the PL quenching of the above noble-metal NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs, TRPL spectroscopy measurement was carried out, and the corresponding

results are given in Fig. 7D. It can be seen that the PL decay curves of all the above samples can be fitted by a biexponential function (eqn (1)). According to the two emission lifetimes obtained from the fitting function (listed in the inset of Fig. 7B), the average emission lifetime could be calculated for comparing the overall emission decay behaviors of the above samples (eqn (3)).

$$\tau_A = (A_1\tau_1^2 + A_2\tau_2^2)/(A_1\tau_1 + A_2\tau_2) \quad (3)$$

The results show that the noble-metal NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs possess shorter average lifetimes as compared to the CaNb<sub>2</sub>O<sub>6</sub>-600 NFs (~5.94 ns). The quenched PL intensities and the shortened lifetimes of the noble-metal NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs indicate the existence of a non-radiative quenching channel due to the photoinduced interfacial electron transfer from CaNb<sub>2</sub>O<sub>6</sub> NFs to the adhesive noble metal NPs. When only exciting the interband transition of CaNb<sub>2</sub>O<sub>6</sub> in the noble-metal NP-decorated CaNb<sub>2</sub>O<sub>6</sub> NFs, the noble-metal NPs can serve as electron sinks to accept the photoinduced electrons from the CaNb<sub>2</sub>O<sub>6</sub> NFs, thereby suppressing the recombination process of photoinduced charge carriers in the CaNb<sub>2</sub>O<sub>6</sub> NFs. Further investigations found that the average lifetime of the Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (~3.61 ns) was shorter than that of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs (~5.52 ns). The shorter average lifetime of the Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs manifests that as for the role of the “electron sink” effect, Pt NPs are more effective for enhancing the photocatalytic activity than Au NPs. However, in our work, the actual photocatalytic activity of the Pt<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs was much lower than that of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs upon UV-visible light irradiation (please note that Au LSPR can be excited by visible light irradiation). This result suggests that the LSPR of Au NPs plays the leading role in enhancing the photocatalytic activity of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs. Finally, the stability of the as-fabricated Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs was investigated through a cycling test on photocatalytic overall water splitting upon UV-visible light irradiation. As shown in Fig. 7E and S20,† after three cycles, the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs with the original phase structure still possess ~94.9% of their initial photocatalytic activity in the first cycle, which reveals the good photocatalytic stability of the Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs. Importantly, our work is the first attempt to fabricate an electrospun CaNb<sub>2</sub>O<sub>6</sub>-based NF photocatalyst for realizing the stoichiometric splitting of pure water into H<sub>2</sub> and O<sub>2</sub> upon UV-visible irradiation. Furthermore, the photocatalytic H<sub>2</sub>-production activity of our produced Au<sub>1</sub>/CaNb<sub>2</sub>O<sub>6</sub> NFs in the absence of a sacrificial agent is higher than that of all the reported CaNb<sub>2</sub>O<sub>6</sub>-based photocatalysts (Fig. 7F).

### 3 Conclusions

In summary, CaNb<sub>2</sub>O<sub>6</sub> NFs with a NP-stacked 1D porous nanostructure have been fabricated by using an electrospinning technique combined with a high-temperature calcination process. The above unique nanostructure led to the formation of many continuous homogeneous interfaces in the CaNb<sub>2</sub>O<sub>6</sub> NFs. These homogeneous interfaces could boost the inter-particle charge migration for generating long-lived charge



carriers. Thus, the photocatalytic activity of  $\text{CaNb}_2\text{O}_6$  NFs for pure water splitting was  $\sim 7.7$  times higher than that of the  $\text{CaNb}_2\text{O}_6$  NPs under UV-visible light irradiation. More importantly, the introduction of plasmonic Au NPs into  $\text{CaNb}_2\text{O}_6$  NFs could effectively extend the visible-light absorption range and further enhance the photoinduced charge transfer, thereby leading to  $\sim 13.1$ -fold enhancement of the photocatalytic activities for both  $\text{H}_2$  and  $\text{O}_2$  production as compared to the pure  $\text{CaNb}_2\text{O}_6$  NFs. We have also demonstrated that the co-excitation of Au LSPR and  $\text{CaNb}_2\text{O}_6$  interband transition is the prerequisite for realizing this remarkable enhancement of photocatalytic water splitting. The excited  $\text{CaNb}_2\text{O}_6$  could not only create highly active charge carriers to reduce the reaction kinetic barrier of water splitting, but also enhance its conductivity to boost the hot electron transfer for improving the hot exciton separation. Thus, the plasmon-excited hot electrons and holes over Au NPs can enhance the photocatalytic activity of Au/ $\text{CaNb}_2\text{O}_6$  NFs for splitting pure water into  $\text{H}_2$  and  $\text{O}_2$ . Our work reported a new wide-bandgap fermite semiconductor photocatalyst of 1D  $\text{CaNb}_2\text{O}_6$  NFs for photocatalytic splitting of pure water into  $\text{H}_2$  and  $\text{O}_2$ . It also provides a new plasmon-dominant synergy strategy to simultaneously extend the light absorption range and improve the charge-carrier kinetics of 1D wide-bandgap semiconductor NFs for remarkably enhancing photocatalytic overall water splitting.

## 4 Experimental

### 4.1 Fabrication of the samples

**4.1.1 Fabrication of  $\text{CaNb}_2\text{O}_6$  NFs.** The  $\text{CaNb}_2\text{O}_6$  NFs were fabricated by using an electrospinning method combined with the subsequent calcination at 500 °C, 600 °C and 700 °C, respectively. During the preparation of the precursor solution, 0.095 g of calcium acetylacetonate ( $\text{C}_{10}\text{H}_{14}\text{CaO}_4$ ) and 0.3225 g of niobium oxalate ( $\text{C}_{10}\text{H}_5\text{NbO}_{20}$ ) were added into 10 mL of N, N-dimethylformamide (DMF) with constant stirring. Then, 1.0 g of poly vinyl pyrrolidone (PVP) power (Mw = 1 300 000) was slowly added to the above mixture solution under vigorous stirring for 16 h. Afterward, this mixture solution of PVP/DMF/ $\text{C}_{10}\text{H}_{14}\text{CaO}_4$ / $\text{C}_{10}\text{H}_5\text{NbO}_{20}$  was filled into a plastic syringe for electrospinning. After the electrospinning treatment, the NFs of the PVP/ $\text{C}_{10}\text{H}_{14}\text{CaO}_4$ / $\text{C}_{10}\text{H}_5\text{NbO}_{20}$  composite could be obtained by applying an electric voltage of 10 kV with a distance of  $\sim 15$  cm between the needle tip and the tinfoil receiver. Finally, the as-electrospun composite NFs were heated to 500 °C, 600 °C and 700 °C, respectively, with a rising time of 4 h and kept for 2 h at the required temperature. The  $\text{CaNb}_2\text{O}_6$  NFs fabricated through the calcination treatment at 500 °C, 600 °C and 700 °C were denoted as  $\text{CaNb}_2\text{O}_6$ -500 NFs,  $\text{CaNb}_2\text{O}_6$ -600 NFs, and  $\text{CaNb}_2\text{O}_6$ -700 NFs respectively.

**4.1.2 Fabrication of Au NP-decorated  $\text{CaNb}_2\text{O}_6$  NFs.** In a typical procedure, 0.095 g of  $\text{C}_{10}\text{H}_{14}\text{CaO}_4$ , 0.3225 g of  $\text{C}_{10}\text{H}_5\text{NbO}_{20}$ , 0.68 mg of chloroauric acid ( $\text{HAuCl}_4$ ) (0.25 at%, Au to Ca), and 1.0 g of PVP were added into 10 mL of DMF in sequence under constant stirring. After vigorous stirring for 16 h, the obtained precursor solution was moved into a plastic syringe for electrospinning. After the electrospinning

treatment, the composite NFs of PVP/ $\text{C}_{10}\text{H}_{14}\text{CaO}_4$ / $\text{C}_{10}\text{H}_5\text{NbO}_{20}$ / $\text{HAuCl}_4$  could be achieved by applying an electric voltage of 10 kV with a distance of  $\sim 15$  cm between the needle tip and the tinfoil receiver. Finally, the as-electrospun composite NFs were heated to 600 °C with a rising time of 4 h and kept for 2 h at the required temperature. The as-fabricated Au-decorated  $\text{CaNb}_2\text{O}_6$  NFs were denoted as  $\text{Au}_1/\text{CaNb}_2\text{O}_6$  NFs, where 1 is the molar ratio (%) of Au to Ca in the precursor solution. By using the same method,  $\text{Au}_{0.25}/\text{CaNb}_2\text{O}_6$  NFs,  $\text{Au}_{0.5}/\text{CaNb}_2\text{O}_6$  NFs,  $\text{Au}_{0.75}/\text{CaNb}_2\text{O}_6$  NFs,  $\text{Au}_{1.25}/\text{CaNb}_2\text{O}_6$  NFs, and  $\text{Pt}_1/\text{CaNb}_2\text{O}_6$  NFs were fabricated, respectively, for investigating the photocatalytic activity for overall water splitting.

### 4.2 Characterization

An X-ray diffractometer (XRD; XRD-6000, Shimadzu) with a Cu  $K\alpha$  line of 0.1541 nm was used to study the crystallization and the phase transition. The morphology and structure of the as-prepared samples were observed by using a scanning electron microscope (SEM; S-4800, Hitachi) and transmission electron microscope (TEM; JEM-2100, JEOL). UV-vis absorption spectra were recorded with a Lambda 750 UV/Vis/NIR spectrophotometer (PerkinElmer, USA). X-ray photoelectron spectroscopy (XPS) was performed on a VG-ESCALAB LKII instrument with a Mg  $K\alpha$  ADES ( $h\nu = 1253.6$  eV) source at a residual gas pressure below  $10^{-8}$  Pa. Photoluminescence (PL) spectra were recorded using a fluorescence spectrophotometer (F-4600, Hitachi) equipped with a 150 W Xe lamp as the excitation light source. The decay curves of the as-prepared samples were obtained on an FLS920 fluorescence lifetime spectrophotometer (Edinburgh Instruments, UK) under the excitation of a hydrogen flash lamp with the wavelength at 280 nm (nF900; Edinburgh Instruments). Thermogravimetry and differential scanning calorimetry (TG-DSC) were implemented by using a NETZSCH STA 449F3 simultaneous thermal analyser under an air atmosphere in the range of 30–800 °C. Fourier transform infrared spectroscopy (FT-IR) spectra were recorded by using a Nicolet iS10 FT-IR spectrometer in the range of 500–4000  $\text{cm}^{-1}$ . The specific surface areas of the samples was investigated through a Micromeritics ASPA-2020 instrument and analysed by the Brunauer–Emmett–Teller (BET) method.

### 4.3 Computational method

**4.3.1 Density functional theory simulation.** The Cambridge Serial Total Energy Package (CASTEP) has been used for the band structure, density of states, geometry optimization, and optical property calculations, which is based on DFT using a plane-wave pseudopotential method. We use the generalized gradient approximation (GGA) in the scheme of Perdew–Burke–Ernzerhof (PBE) to describe the exchange–correlation functional. A cut-off energy of 400 eV was chosen for the  $\text{CaNb}_2\text{O}_6$  crystal. The Brillouin-zone sampling mesh parameters for the  $k$ -point set are  $1 \times 1 \times 1$ . In the optimization process, the convergence criteria applied were  $1 \times 10^{-6}$  eV per atom.

**4.3.2 3D finite-difference-time-domain (FDTD) simulation.** The computational simulations were performed with the 3D finite-difference-time-domain method (FDTD, commercial

software package, Ansys Lumerical 2020 R2 Launcher) with perfectly matched layer (PML) boundary conditions. The dielectric function of  $\text{CaNb}_2\text{O}_6$  was calculated by the DFT simulation mentioned above. According to our experimental results from SEM and TEM images, a model of simplified Au/ $\text{CaNb}_2\text{O}_6$  NFs was constructed with a  $\text{CaNb}_2\text{O}_6$  NF and three Au NPs with different positions in the  $\text{CaNb}_2\text{O}_6$  NF, in which the diameter of  $\text{CaNb}_2\text{O}_6$  NF was fixed at 100 nm, and the size of the Au NPs for the Au/ $\text{CaNb}_2\text{O}_6$  NF was determined to be 10 nm. An incident plane wave was propagated from the  $x$  axis and polarized along the  $y$  axis. The wavelength was set at 550 nm. The override mesh cell size used was  $0.2 \times 0.2 \times 0.2$  nm. The Au/ $\text{CaNb}_2\text{O}_6$  NF was surrounded by water with a refractive index of 1.33.

#### 4.4 Photocatalytic overall water splitting

5 mg of the as-fabricated samples and 10 mL of deionised water were added into a 40 mL quartz reactor, regularly. Then, the quartz reactor was blocked with a rubber plug, followed by the ventilation of argon gas for 15 minutes to drive off the residual air. Subsequently, the quartz reactor was exposed to UV-vis light (300 W Xe lamp without a filter, PLS-SXE300UV). The composition of the gas product from the upper space above the liquid in the quartz reactor was periodically analysed by using a gas chromatograph (GC) equipped with a thermal conductivity detector (TCD) (Analytical Instrument, SP-3420A, Beifen-Ruili). The amount of  $\text{H}_2\text{O}_2$  produced during the photocatalytic oxidation of  $\text{H}_2\text{O}$  over the  $\text{CaNb}_2\text{O}_6$  NPs was tested through the following process: The photocatalytic reaction solution was centrifuged at 8000 rpm for 5 min to remove the residual photocatalyst. 1 mL of potassium hydrogen phthalate ( $\text{C}_8\text{H}_5\text{KO}_4$ , 0.1 M) and 1 mL of KI solution (0.4 M) were added into the above solution for further analysis by UV-visible spectroscopy (PERSEE TU-1950) on the basis of the absorbance at 350 nm.

#### 4.5 Electrochemical measurement

The Bode phase plots were obtained by using an electrochemical workstation (Autolab PGSTAT302N). 5 mg of as-fabricated samples were coated on ITO glass with an effective area of  $1 \text{ cm} \times 1 \text{ cm}$ , which acted as working electrodes. Pt wire and Ag/AgCl electrodes acted as the counter and reference electrodes, respectively. And, 1 M  $\text{Na}_2\text{SO}_3$  aqueous solution was used as the electrolyte. The photocurrent and Mott tests are similar to the above, and the electrolyte is 0.2 M  $\text{Na}_2\text{SO}_4$ .

## Author contributions

Jiaming Zhang: Data curation, Methodology, and Writing - Original Draft. Xiaoyi Jiang: Software, Formal analysis, and Validation. Jindou Huang: Software, Formal analysis, and Validation. Wei Lu: Validation and Writing - review & editing. Zhenyi Zhang: Conceptualization, Validation, Formal analysis, Resources, Writing - review & editing, and Supervision.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (Grant Nos. 12074055 and 51772041), Natural Science Foundation of Liaoning Province for Excellent Young Scholars (2022-YQ-13), Liaoning BaiQianWan Talents Program, and Dalian Science Foundation for Distinguished Young Scholars (No 2018RJ05).

## Notes and references

- 1 S. Xu and E. A. Carter, *Chem. Rev.*, 2019, **119**, 6631–6669.
- 2 C. Li, Y. Xu, W. Tu, G. Chen and R. Xu, *Green Chem.*, 2017, **19**, 882–899.
- 3 J. W. Wang, L. Jiang, H. H. Huang, Z. Han and G. Ouyang, *Nat. Commun.*, 2021, **12**, 4276.
- 4 H. Lei, Q. He, M. Wu, Y. Xu, P. Sun and X. Dong, *J. Hazard. Mater.*, 2022, **421**, 126696.
- 5 J. Li, X. Wu and S. Liu, *Acta Phys. Sin. Ch. Ed.*, 2021, **37**, 2009038.
- 6 Z. Jiang, Q. Chen, Q. Zheng, R. Shen, P. Zhang and X. Li, *Acta Phys. Sin. Ch. Ed.*, 2021, **37**, 2010059.
- 7 H. Chang, J. Liu, Z. Dong, D. Wang, Y. Xin, Z. Jiang and S. Tang, *Acta Phys. Sin. Ch. Ed.*, 2021, **40**, 1595–1603.
- 8 M. Li, R. Guan, J. Li, Z. Zhao, J. Zhang, C. Dong, Y. Qi and H. Zhai, *Acta Phys. Sin. Ch. Ed.*, 2020, **39**, 1437–1443.
- 9 A. Kumar, V. Navakoteswara Rao, A. Kumar, M. Venkatakrishnan Shankar and V. Krishnan, *ChemPhotoChem*, 2020, **4**, 427–444.
- 10 G. Sun, S. Mao, D. Ma, Y. Zou, Y. Lv, Z. Li, C. He, Y. Cheng and J. Shi, *J. Mater. Chem. A.*, 2019, **7**, 15278.
- 11 P. Niu, J. Dai, X. Zhi, Z. Xia, S. Wang and L. Li, *InfoMat*, 2021, **3**, 931–961.
- 12 D. Ma, Z. Wang, J. Shi, Y. Zou, Y. Lv, X. Ji, Z. Li, Y. Cheng and L. Wang, *J. Mater. Chem. A.*, 2020, **8**, 11031.
- 13 A. Kumar and V. Krishnan, *Adv. Funct. Mater.*, 2021, 2009807.
- 14 G. Sun, B. Xiao, H. Zheng, J. Shi, S. Mao, C. He, Z. Li and Y. Cheng, *J. Mater. Chem. A.*, 2021, **9**, 9735.
- 15 A. Kumar, V. Navakoteswara Rao, A. Kumar, A. Mushtaq, L. Sharma, A. Halder, S. K. Pal, M. V. Shankar and V. Krishnan, *ACS Appl. Energy Mater.*, 2020, **3**, 12134–12147.
- 16 Q. Wang and K. Domen, *Chem. Rev.*, 2020, **120**, 919–985.
- 17 N. Som, V. Mankad and P. Jha, *Int. J. Hydrogen Energy*, 2018, **47**, 21634–21641.
- 18 S. Kumar, A. Kumar, A. Kumar and V. Krishnan, *Catal. Rev.: Sci. Eng.*, 2019, **62**, 1–60.
- 19 A. C. Malingowski, P. W. Stephens, A. Huq, Q. Huang, S. Khalid and P. G. Khalifah, *Inorg. Chem.*, 2012, **51**, 6096–6103.
- 20 C. Xu and P. Lv, *Chin. J. Struct. Chem.*, 2021, **40**, 1223–1230.
- 21 X. Ning and G. Lu, *Nanoscale*, 2020, **12**, 1213–1223.
- 22 S. Fang and Y. H. Hu, *Int. J. Energy Res.*, 2019, **43**, 1082–1098.
- 23 N. C. Hildebrandt, J. Soldat and R. Marschall, *Small*, 2015, **11**, 2051–2057.
- 24 Z. Wang, J. Hong, S.-F. Ng, W. Liu, J. Huang, P. Chen and W.-J. Ong, *Acta Phys.-Chim. Sin.*, 2020, 2011033.

- 25 A. Kumar, A. Kumar and V. Krishnan, *ACS Catal.*, 2020, **10**, 10253–10315.
- 26 Y. Su, L. Peng, C. Du and X. Wang, *J. Phys. Chem. C*, 2011, **116**, 15–21.
- 27 A. Kumar, M. Kumar, V. Navakoteswara Rao, M. Venkatakrishnan Shankar, S. Bhattacharya and V. Krishnan, *J. Mater. Chem. A*, 2021, **9**, 17006–17018.
- 28 O. I. Velikokhatnyi and P. N. Kumta, *J. Power Sources*, 2012, **202**, 190–199.
- 29 S. Liu, P. Li, N. Umezawa, W. Zhou, H. Abe and G. Wang, *Catal. Sci. Technol.*, 2019, **9**, 3619–3622.
- 30 I.-S. Cho, S. Lee, J. H. Noh, D. W. Kim, D. K. Lee, H. S. Jung, D.-W. Kim and K. S. Hong, *J. Mater. Chem.*, 2010, **20**, 3979.
- 31 I.-S. Cho, D. W. Kim, C. M. Cho, J.-S. An, H.-S. Roh and K. S. Hong, *Solid State Sci.*, 2010, **12**, 982–988.
- 32 Y. Zhang, C. Liu, G. Pang, S. Jiao, S. Zhu, D. Wang, D. Liang and S. Feng, *Eur. J. Inorg. Chem.*, 2010, **2010**, 1275–1282.
- 33 I.-S. Cho, S. T. Bae, D. H. Kim and K. S. Hong, *Int. J. Hydrogen Energy*, 2010, **35**, 12954–12960.
- 34 I.-S. Cho, S. T. Bae, D. K. Yim, D. W. Kim and K. S. Hong, *J. Am. Ceram. Soc.*, 2009, **92**, 506–510.
- 35 Y. Hong, S.-H. Jeon, H. Jeong and H. Ryu, *Ceram. Int.*, 2021, **47**, 7814–7823.
- 36 S. Choi, S. Kim, S. Lim and H. Park, *J. Phys. Chem. C*, 2010, **114**, 16475–16480.
- 37 Z. Zhang, Z. Wang, S. Cao and C. Xue, *J. Phys. Chem. C*, 2013, **117**, 25939–25947.
- 38 Z. Zhang, X. Jiang, B. Liu, L. Guo, N. Lu, L. Wang, J. Huang, K. Liu and B. Dong, *Adv. Mater.*, 2018, **30**, 1705221.
- 39 X. Fang, Q. Shang, Y. Wang, L. Jiao, T. Yao, Y. Li, Q. Zhang, Y. Luo and H. L. Jiang, *Adv. Mater.*, 2018, **30**, 1705112.
- 40 H.-M. Chiu, T.-H. Yang, Y.-C. Hsueh, T.-P. Perng and J.-M. Wu, *Appl. Catal., B*, 2015, **163**, 156–166.
- 41 H. Sun, S. Zeng, Q. He, P. She, K. Xu and Z. Liu, *Dalton Trans.*, 2013, 1–3.
- 42 S. K. Cushing, J. Li, F. Meng, T. R. Senty, S. Suri, M. Zhi, M. Li, A. D. Bristow and N. Wu, *J. Am. Chem. Soc.*, 2012, **134**, 15033–15041.
- 43 Z. Liu, W. Hou, P. Pavaskar, M. Aykol and S. B. Cronin, *Nano Lett.*, 2011, **11**, 1111–1116.
- 44 I. S. Cho, D. W. Kim, T. H. Noh, S. Lee, D. K. Yim and K. S. Hong, *J. Nanosci. Nanotechnol.*, 2010, **10**, 1196–1202.
- 45 S. Cao, B. Shen, T. Tong, J. Fu and J. Yu, *Adv. Funct. Mater.*, 2018, **28**, 1800136.
- 46 T. Tachikawa, T. Ochi and Y. Kobori, *ACS Catal.*, 2016, **6**, 2250–2256.
- 47 Y.-J. Hsiao, C.-W. Liu, B.-T. Dai and Y.-H. Chang, *J. Alloys Compd.*, 2009, **475**, 698–701.
- 48 E. V. Pean, S. Dimitrov, C. S. De Castro and M. L. Davies, *Phys. Chem. Chem. Phys.*, 2020, **22**, 28345–28358.
- 49 P. Bera, K. Priolkar, A. Gayen, P. R. Sarode, M. S. Hegde, S. Emura, R. Kumashiro, V. Jayara and G. N. Subbanna, *Chem. Mater.*, 2013, **15**, 2049–2060.
- 50 X. Jiang, J. Huang, Z. Bi, W. Ni, G. Gurzadyan, Y. Zhu and Z. Zhang, *Adv. Mater.*, 2022, e2109330.
- 51 W. Guo, Q. Qin, L. Geng, D. Wang, Y. Guo and Y. Yang, *J. Hazard. Mater.*, 2016, **308**, 374–385.
- 52 X. Wang, C. Liow, A. Bisht, X. Liu, T. C. Sum, X. Chen and S. Li, *Adv. Mater.*, 2015, **27**, 2207–2214.
- 53 L. Zhang, N. Ding, L. Lou, K. Iwasaki, H. Wu, Y. Luo, D. Li, K. Nakata, A. Fujishima and Q. Meng, *Adv. Funct. Mater.*, 2019, **29**, 1806774.
- 54 S. Cabrini, G. Léron del, A. M. Schwartzberg, T. Mokari, J. Lee, S.-H. Lee, M. S. Kim, H. Shin and J. Kim, *Proc. SPIE*, 2014, **9161**, 916109.
- 55 G.-Y. Yao, Q.-L. Liu and Z.-Y. Zhao, *Catalysts*, 2018, **8**, 236.
- 56 H. Song, X. Meng, T. D. Dao, W. Zhou, H. Liu, L. Shi, H. Zhang, T. Nagao, T. Kako and J. Ye, *ACS Appl. Mater. Interfaces*, 2018, **10**, 408–416.
- 57 M. Dozzi, A. Candeo, G. Marra, C. D'Andrea, G. Valentini and E. Selli, *J. Phys. Chem. C*, 2018, **133**, 14326–14335.