

Cite this: *J. Mater. Chem. C*, 2022, **10**, 15394

## Luminescent chiral triangular prisms capable of forming double helices for detecting traces of acids and anion recognition†

Lifang Bian,<sup>ab</sup> Min Tang,<sup>ib</sup> Jiali Liu,<sup>b</sup> Yimin Liang,<sup>b</sup> Lin Wu<sup>b</sup> and Zhichang Liu<sup>ib\*</sup>

Orchestrating stimuli-responsiveness, molecular recognition, and self-assembly in macrocycles plays a vital role in the preparation of multifunctional materials. Herein, we report a pair of triangular prismatic enantiomers (**R**)- and (**S**)- $\Delta$  based on tetraphenylethylene (TPE), which assemble into left- and right-handed double helices, respectively, in their single-crystal X-ray superstructures. Due to the geometrical constraint of triangles to the phenylene rotation within TPE, their emission is enhanced significantly. In addition, their fluorescence and circularly polarized luminescence change from blue to yellow in response to traces of acids in solvents, which, combined with enhanced intensity, makes them sensitive indicators for the quantitative detection of the acid present in common organic solvents such as  $\text{CDCl}_3$ ,  $\text{CH}_2\text{Cl}_2$ , and  $\text{CHCl}_3$ , with a detection limit as low as  $5 \times 10^{-7}$  M. Furthermore, the cavity of triangles can bind  $\text{I}_3^-$  to form host-guest adducts by single-crystal-to-single-crystal transformation.

Received 19th August 2022,  
Accepted 22nd September 2022

DOI: 10.1039/d2tc03506e

rsc.li/materials-c

## Introduction

Multi-purpose application requirements have brought challenges to the design of functional molecules. By embracing macrocyclic chemistry, especially in relation to molecular recognition and self-assembly, chemists can design sophisticated host molecules with multifunctionality. Thanks to their rigid geometries and enforced cavities, shape-persistent macrocycles, such as calixarenes,<sup>1–3</sup> cucurbiturils,<sup>4,5</sup> pillararenes,<sup>6</sup> and cycloparaphenylenes,<sup>7,8</sup> as well as various cages,<sup>9–19</sup> have been investigated extensively. Among them, molecular triangles<sup>20–23</sup> have exhibited considerable potential in storage, sensing, separation, catalysis, *etc.* on account of their triangular cavities being able to encapsulate selectively guest molecules of matching size and stereoelectronic properties.<sup>24–29</sup> In addition, the small internal angle inside the triangles enforces interactions between their side units enhancing<sup>30</sup> some of their properties.

Aggregation-induced emission (AIE) of tetraphenylethylene (TPE) has been applied widely in fluorescent probes,<sup>31,32</sup> bio-imaging agents,<sup>33,34</sup> chemical sensors,<sup>35–37</sup> and circularly polarized luminescence (CPL).<sup>38,39</sup> The  $D_{2h}$  symmetry and tetratopic reaction

positions of TPE make it an ideal building block for constructing macrocycles and cages.<sup>40–44</sup> Employing TPE as an organic linker enhances significantly the luminescence of these molecules as a result of the restriction of the phenylene rotation by either geometrical constraints or guest complexation.<sup>45–48</sup> Taking advantage of the enhanced emission intensity of TPE, chiral macrocycles and cages possess hierarchical structural complexity and functionality involving chiral recognition and sensing, CPL signal, and chiral superstructures.<sup>16,49</sup>

Herein, we report (Fig. 1) a pair of TPE-incorporated enantiomeric molecular triangles ( $\text{RRRRRRRRRRRR}$ )- $\Delta$  [(**R**)- $\Delta$ ] and ( $\text{SSSSSSSSSSSS}$ )- $\Delta$  [(**S**)- $\Delta$ ], which, as confirmed by single-crystal X-ray diffraction (SCXRD), can (i) assemble into left- (*M*) and right-handed (*P*)-double helices, respectively, as a result of chirality transfer. (ii) The enhanced emission intensity of the geometrically constrained TPE, combining with (iii) the trace acid-responsive emission, makes them (iv) sensitive indicators for the detection of the amount of acid in organic solvents to a limit of  $5 \times 10^{-7}$  M. Moreover, their triangular prismatic cavities can also (v) bind triiodide anions ( $\text{I}_3^-$ ) to form host-guest adducts through a single-crystal-to-single-crystal (SCSC) transformation.

## Results and discussion

Enantiomeric (**R**)- and (**S**)- $\Delta$  were synthesized (Fig. 1) by a [3+6] cycloimination between tetrakis(4-formylphenyl)ethylene (1) with (1*R*,2*R*)- or (1*S*,2*S*)-diaminocyclohexane (2) in 88% and 90% yields, respectively. Their formation was confirmed by <sup>1</sup>H

<sup>a</sup> Department of Chemistry, Zhejiang University, Hangzhou, Zhejiang, 310027, China. E-mail: liu@westlake.edu.cn

<sup>b</sup> Key Laboratory of Precise Synthesis of Functional Molecules of Zhejiang Province, Department of Chemistry, School of Science, Westlake University, 18 Shilongshan Road, Hangzhou, Zhejiang, 310024, China

† Electronic supplementary information (ESI) available. CCDC 2114992–2114994. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2tc03506e>



Fig. 1 Synthesis of **(R)-Δ** as well as side-on and top views of its schematic representation.

and  $^{13}\text{C}$  NMR spectroscopies (Fig. S1–S4, ESI $^\dagger$ ), high-resolution mass spectrometry (Fig. S5, ESI $^\dagger$ ), and FT-IR spectroscopy (Fig. S6, ESI $^\dagger$ ).


Single crystals of **(R)-** and **(S)-Δ** suitable for X-ray crystallography were obtained by slow liquid–liquid diffusion of MeOH into their solutions in  $\text{CHCl}_3$ . SCXRD Analysis revealed

(Fig. 2a and Table S1, ESI $^\dagger$ ) their triangular prismatic geometry wherein three TPE units are linked, in a compact manner, by six diaminocyclohexanes to form a triangular channel (diameter =  $\sim 4$  Å), thus preventing the phenylene rotation of TPE. In the X-ray superstructure (Fig. 2b) of **(R)-Δ**, adjacent triangles bite together through complementary van der Waals interactions (Fig. S7, ESI $^\dagger$ ) between the sides of the triangular prisms to form a **(M)**-single helix. Furthermore, two single helices with complementary configurations are intertwined (Fig. 2c) to form stereocontrolled **(M)**- and **(P)**-double helices from **(R)**- and **(S)-Δ** respectively, wherein each pitch is composed of eight triangles with a length of 5.00 nm and a diameter of 2.5 nm.

The photophysical properties of **(R)**- and **(S)-Δ** in their crystal states were first investigated under ambient conditions. Upon irradiation with 365 nm UV light, block crystals of both **(R)**- and **(S)-Δ** exhibit green-yellow emission (Fig. S8, ESI $^\dagger$ ). As shown in Fig. S9 (ESI $^\dagger$ ), their steady-state photoluminescence spectra showed a green-yellow emission band at around 530 nm with lifetime of 4.59 and 4.49 ns (Fig. S12 and Table S2, ESI $^\dagger$ ) as well as quantum efficiencies of 27.7% and 26.2% (Table S3, ESI $^\dagger$ ) for **(R)**- and **(S)-Δ**, respectively. When cleaning a flask containing **(R)-Δ** using commercial grade  $\text{CH}_2\text{Cl}_2$ , we discovered serendipitously that the fluorescence emission of the solution upon irradiation with 365 nm-UV light changed from the original blue to yellow. This observation inspired us to measure the fluorescence spectra of **(R)-Δ** in commercial grade  $\text{CH}_2\text{Cl}_2$  and  $\text{CHCl}_3$  at concentrations as low as  $1 \times 10^{-4}$ ,  $1 \times 10^{-5}$ , and



Fig. 2 Single-crystal X-ray (super)structures of triangles. (a) Side-on (tubular) and top views (space-filling) of **(R)-Δ**. C, tan; N, blue, H, white. (b) **(M)**-single helix (top) assembled through complementary bite (down) between two adjacent **(R)-Δ**. (c) Mirror-symmetrical **(M)**- and **(P)**-double helices formed by entangling two single helices assembled from enantiomeric **(R)**- and **(S)-Δ**, respectively. One strand in both double helices is depicted in orange tubular representation, while the other in blue space-filling. Hydrogen atoms are omitted for the sake of clarity.

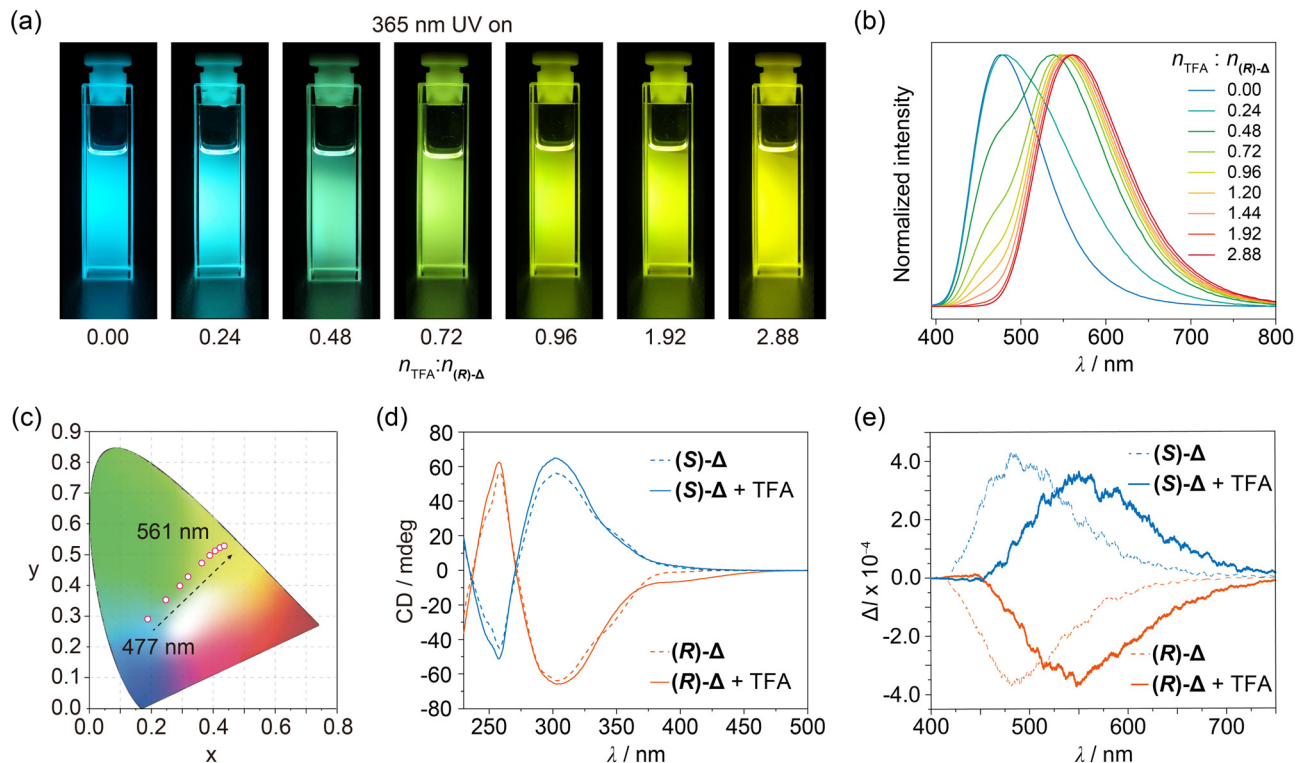

**Fig. 3** Photophysical properties of (*R*- and (*S*)- $\Delta$ . (a) Luminescence photographs taken upon shining 365 nm UV light. (b) Fluorescence spectra upon excitation at 380 nm. (c) Trajectory of tuning colors shown in the CIE coordinate diagram of solutions ( $1 \times 10^{-5}$  M) of (*R*)- $\Delta$  in  $\text{CHCl}_3$  containing different amounts of TFA relative to (*R*)- $\Delta$  ranging from 0 to 2.88 equiv. (d) CD and (e) CPL spectra of solutions ( $2 \times 10^{-4}$  M) of (*R*- and (*S*)- $\Delta$  in deacidified  $\text{CHCl}_3$  (dash line) and in acidified  $\text{CHCl}_3$  with TFA ( $2.88 \times 10^{-5}$  M, solid line).

$1 \times 10^{-6}$  M, which exhibit (Fig. S10, ESI<sup>†</sup>) a clear trend in emission color from blue ( $\sim 480$  nm) to yellow ( $\sim 560$  nm) upon decreasing concentrations. We believe that the change in emission color might result from traces of acid in these solvents. Next, we measured the fluorescence spectra of (*R*)- $\Delta$  in deacidified  $\text{CH}_2\text{Cl}_2$  and  $\text{CHCl}_3$  with  $\text{K}_2\text{CO}_3$  at the same concentrations and discovered that they show no change in emission, confirming that traces of acid in solvents can change the emission of (*R*)- $\Delta$ . We performed a series of photophysical characterizations to compare properties of (*R*- and (*S*)- $\Delta$  in deacidified and quantitatively acidified  $\text{CHCl}_3$ , respectively. UV-Vis Spectra of solutions ( $1 \times 10^{-5}$  M) of (*R*- and (*S*)- $\Delta$  in deacidified  $\text{CHCl}_3$  show (Fig. S11, ESI<sup>†</sup>) characteristic peaks at 272, 310, and 345 nm, while the same solutions exhibit (Fig. 3a) bright blue emission upon irradiation with 365 nm-UV light. Fluorescence spectra recorded on the same solutions demonstrate (Fig. 3b) an emission band at  $\sim 477$  nm upon excitation at 380 nm, which has (Fig. S13 and Table S4, ESI<sup>†</sup>) a typical fluorescence feature with lifetimes of 2.29 and 2.52 ns and high quantum efficiencies of 25.5% and 23.4% (Table S5, ESI<sup>†</sup>) for (*R*- and (*S*)- $\Delta$ , respectively. The significantly enhanced emission efficiencies can be ascribed to the restriction of the phenylene rotation within triangles.

Enantiomeric (*R*- and (*S*)- $\Delta$  in deacidified  $\text{CHCl}_3$  lead (Fig. 3d) to mirror-symmetrical negative and positive Cotton effects in circular dichroism (CD) spectra, respectively, while CPL signals of (*R*- and (*S*)- $\Delta$  are (Fig. 3e) also mirror-symmetrical at 484 nm

with dissymmetry factors ( $g_{\text{lum}}$ ) of  $-5.8 \times 10^{-4}$  and  $6.6 \times 10^{-4}$ , respectively.

Trifluoroacetic acid (TFA) was chosen to prepare quantitatively acidified  $\text{CHCl}_3$ . Upon increasing the molar ratio of  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  from 0 to 2.88 in solutions ( $1 \times 10^{-5}$  M) of (*R*)- $\Delta$  in quantitatively acidified  $\text{CHCl}_3$ , their UV-Vis spectra exhibit (Fig. S11, ESI<sup>†</sup>) a decrease at 345 nm in concert with an enhancement at 365–500 nm, while their emissions show (Fig. 3a and b) a significant redshift from 477 to 561 nm, which covers a multicolor region from blue to green to yellow as shown (Fig. 3c) in the CIE chromaticity diagram. We envision that the protonation of (*R*)- $\Delta$  might narrow the energy gap and thus leading to the redshifted emission. Meanwhile, the more rigid cage stabilized by hydrogen bonding of NH upon protonation can reduce the non-radiative transition of intramolecular excitons and thus exhibiting (Fig. S13 and Table S4, ESI<sup>†</sup>) a longer fluorescence lifetime of 4.87 ns. In order to gain insight into the change in photophysical properties, absorption spectra of (*R*)- $\Delta$  and protonated (*R*)- $\Delta$  were calculated using time-dependent density functional theory (TD-DFT). TD-DFT Data indicate that, upon protonation, the HOMO–LUMO energy gap decreases (Fig. S14, ESI<sup>†</sup>) from 3.53 eV in the case of (*R*)- $\Delta$  to 3.02 eV for the protonated counterpart, an observation which is in line with the redshifts in absorption and emission spectra upon protonation. CD Signals of (*R*- and (*S*)- $\Delta$  solutions in a molar ratio of  $n_{\text{TFA}}:n_{(\text{R})-\Delta} = 2.88$  were (Fig. 3d) slightly enhanced, while their CPL signals were red-shifted (Fig. 3e) from 484 to 550 nm with increased  $g_{\text{lum}}$  of  $-7.5 \times 10^{-4}$  and  $7.6 \times 10^{-4}$ ,

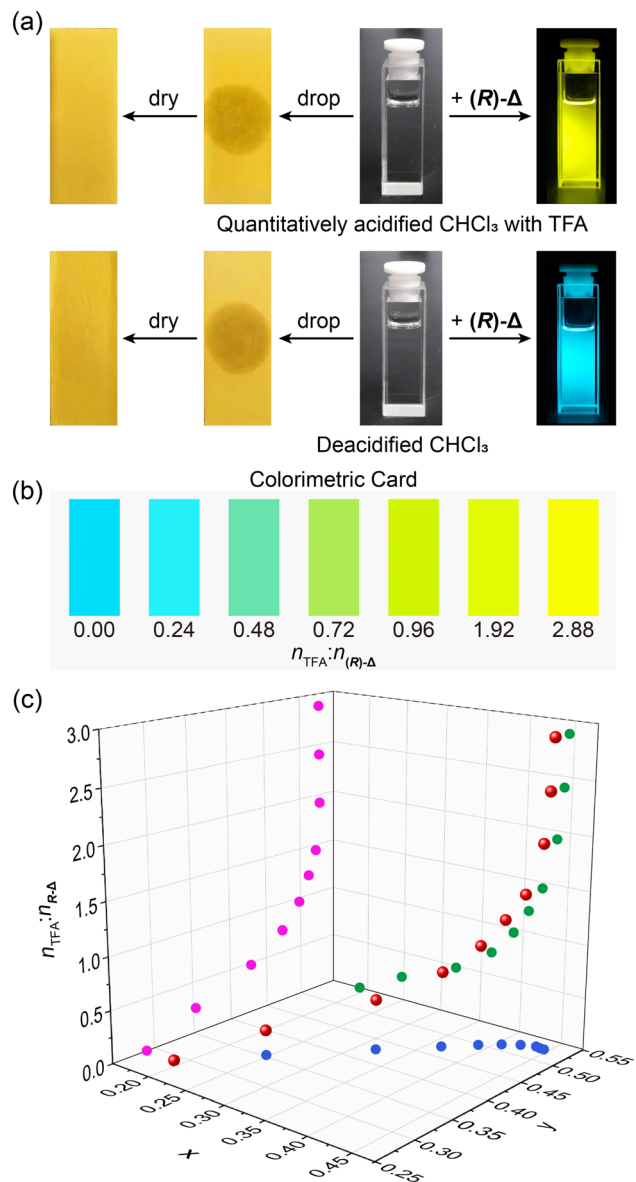


Fig. 4 Detecting traces of acids employing (R)- $\Delta$ . (a) Fluorescence changes of solutions (right) of (R)- $\Delta$  in  $\text{CHCl}_3$  with and without TFA upon shining 365 nm-UV light in comparison with detecting trace acid in the same solvents using pH papers (left). (b) A colorimetric card showing the ability of (R)- $\Delta$  to detect visually amounts of acid in solutions with different  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  ratios. (c) The fitting function based on the PL emission of (R)- $\Delta$  upon changing the  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  ratio from 0.00 to 2.88. The concentration of (R)- $\Delta$  is  $1 \times 10^{-5}$  M.

respectively, thus realizing trace acid-responsive and color tunable CPL signals.

While trace amount of acids in organic solvents can cause undesired consequences, they are difficult to quantify.<sup>50</sup> Based on the trace acid-responsive fluorescence change of (R)- $\Delta$ , we have explored its potential as an indicator to detect trace acids in organic solvents. Upon dropping (Fig. 4a) quantitatively acidified  $\text{CHCl}_3$  with TFA ( $2.88 \times 10^{-5}$  M) and deacidified  $\text{CHCl}_3$  on to two pH papers, respectively, colors of both pH papers did not undergo change. In contrast, when shining

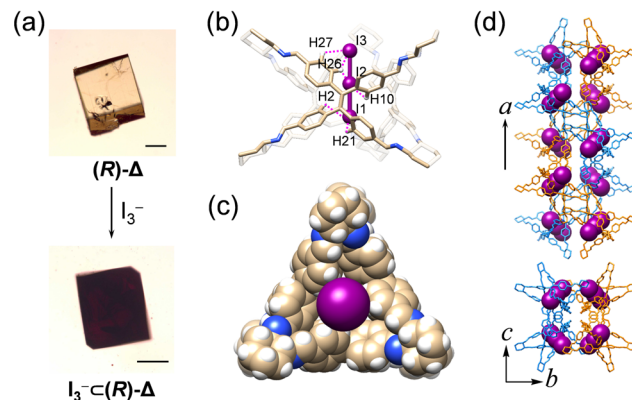


Fig. 5 Anion recognition in (R)- $\Delta$ . (a) Photographs of single crystals of (R)- $\Delta$  and [I<sub>3</sub><sup>-</sup>] $\cdot$ (R)- $\Delta$ . (b) and (c) Superstructure of [I<sub>3</sub><sup>-</sup>] $\cdot$ (R)- $\Delta$  in tubular and (c) space-filling representations exhibiting the encapsulation of I<sub>3</sub><sup>-</sup> inside the cavity of (R)- $\Delta$  by 18 [C-H...I] interactions. C, tan; N, blue; H, white; I, purple. (d) Side-on (top) and top (down) views of the double helical superstructure of [I<sub>3</sub><sup>-</sup>] $\cdot$ (R)- $\Delta$ . Hydrogen atoms are omitted for clarity. One strand in the double helix is depicted in orange tubular representation and the other in blue, while I<sub>3</sub><sup>-</sup> is represented in a space-filling form.

365 nm-UV light on two solutions ( $1 \times 10^{-5}$  M) of (R)- $\Delta$  prepared from the above two solvents, the former ( $n_{\text{TFA}}:n_{(\text{R})-\Delta} = 2.88$ ) exhibits yellow emission, while the latter ( $n_{\text{TFA}}:n_{(\text{R})-\Delta} = 0$ ) is blue, suggesting that the emission of (R)- $\Delta$  is highly sensitive to traces of acid. Upon increasing the molar ratio of  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  from 0 to 2.88 in solutions ( $1 \times 10^{-5}$  M) of (R)- $\Delta$  in  $\text{CHCl}_3$ , their fluorescence colors could be discerned by the naked eye, demonstrating the potential of (R)- $\Delta$  as a visual colorimetric card (Fig. 4b) for rapidly detecting traces of acid in solvents. Moreover, trace amounts of various acids in solvents can be detected quantitatively (Fig. 4c) as equivalent TFA by correlating the relationship between the molar ratio of  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  and the CIE chromaticity coordinates. We detected the acid amount in two commercial  $\text{CDCl}_3$  samples [one with silver foil (C) and the other without (E)] using (R)- $\Delta$ . A solution of (R)- $\Delta$  ( $1 \times 10^{-5}$  M) in  $\text{CDCl}_3$  C exhibited (Fig. S15, ESI<sup>†</sup>) a yellow-green emission in CIE coordinates upon excitation at 380 nm, which is equivalent to a  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  ratio of 0.49, namely,  $0.49 \times 10^{-5}$  M of TFA. In striking contrast, the amount of acid in a solution of (R)- $\Delta$  ( $1 \times 10^{-5}$  M) in  $\text{CDCl}_3$  E is too much and exceeds the detection threshold. When we diluted  $\text{CDCl}_3$  E 100 times with deacidified  $\text{CHCl}_3$  to make a solution of (R)- $\Delta$  ( $1 \times 10^{-5}$  M) in solvent D, the emission of which was measured (Fig. S16, ESI<sup>†</sup>) to correspond to a  $n_{\text{TFA}}:n_{(\text{R})-\Delta}$  ratio of 0.63—that is,  $0.63 \times 10^{-5}$  M of TFA. Considering the 100-fold dilution, the amount of acid in  $\text{CDCl}_3$  E without silver foil is equivalent to  $0.63 \times 10^{-3}$  M of TFA and 129 times higher than that in  $\text{CDCl}_3$  C stabilized with silver foil, suggesting that the addition of silver foil stabilizer can decrease significantly the amount of acid in  $\text{CDCl}_3$ . Similarly, traces of acid in commercial grade  $\text{CH}_2\text{Cl}_2$  and  $\text{CHCl}_3$  were also quantified (Fig. S16, ESI<sup>†</sup>) to be equivalent to  $0.30 \times 10^{-5}$  and  $0.46 \times 10^{-5}$  M of TFA, respectively. Finally, the detection limit was measured (Fig. S17, ESI<sup>†</sup>) to be  $5 \times 10^{-7}$  M.

The channel of  $\sim 4$  Å inside (R)- $\Delta$  can act as an ideal host for binding linear guest molecules. We have investigated the

complexation between linear  $I_3^-$  anions and (**R**)- $\Delta$  through SCSC transformation. Upon slow diffusion of a solution of  $[Bu_4N][I_3]$  in MeOH into the mother liquor containing single crystals of (**R**)- $\Delta$ , yellow crystals changed (Fig. 5a) to black after one day. SCXRD Analysis reveals (Fig. 5) that one  $I_3^-$  anion fills completely the tubular cavities of (**R**)- $\Delta$  to form a host-guest adduct  $[I_3^- \subset (\mathbf{R})-\Delta]$  which assembles into a (*M*)-double helix in a similar cubic unit cell to the one with (**R**)- $\Delta$ .  $I_3^-$  Anions are stabilized (Fig. 5b, Fig. S18 and Table S8, ESI<sup>†</sup>) inside the channel through up to 18 weak  $[C-H \cdots I]$  hydrogen bonding interactions (mean  $[H \cdots I]$  separation  $d_{[H \cdots I]} = \sim 3.4 \text{ \AA}$ ), while the  $Bu_4N^+$  cations are disordered. Although the disordered cations in the single-crystal superstructure cannot be observed, we believe that the Coulombic interaction between cations and  $I_3^-$  is also responsible for the stable binding of  $I_3^-$  anions to the cavity of the triangular prism.

## Conclusions

We have prepared a pair of tetraphenylethylene-based enantiomeric molecular triangles (**R**)- and (**S**)- $\Delta$ . X-Ray crystallographic analysis reveals the stereocontrolled formations of left- and right-handed double helices from triangular prismatic (**R**)- and (**S**)- $\Delta$ , respectively, as a result of chirality transfer, wherein the cavities in the triangles can bind  $I_3^-$  anions to form host-guest adducts through SCSC transformation. Both enantiomers exhibit mirror symmetrical CD and CPL signals, as well as significantly enhanced fluorescence as a result of chiral induction together with the restriction of the phenylene rotation by geometrical constraints. Moreover, trace acid-responsive changes in fluorescence and CPL from blue to yellow have been applied to detect quantitatively the acid content in common organic solvents involving  $CH_2Cl_2$ ,  $CHCl_3$ , and  $CDCl_3$ , with a detection limit as low as  $5 \times 10^{-7} \text{ M}$ . This research demonstrates the integration of self-assembly, molecular recognition, and stimuli-responsiveness in a judiciously designed triangle while, at the same time, providing insight into fabricating multifunctional materials.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We are grateful for financial support from the National Natural Science Foundation of China (21971211 and 22171232), the Natural Science Foundation of Zhejiang Province (2022XHSJJ007), the Qiantang River Talent Foundation (QJD1902029), and Westlake University. We thank Drs. Xiaohu Miao, Zhong Chen, Xingyu Lu, Xiaohu Shi, and Yinjuan Chen for their help in the collection of X-ray diffraction dots, recording UV-Vis, CD, CPL, PL, and NMR spectra, and obtaining mass spectrometric data, respectively. This research was supported by Instrumentation and Service Centers for Molecular Science and for Physical Science, respectively, as well as by Westlake University HPC Center. We thank the

Research Center for Industries of the Future (RCIF) at Westlake University for supporting this work. We also thank the staffs from BL17B beamline of National Facility for Protein Science in Shanghai (NFPS) at Shanghai Synchrotron Radiation Facility, for assistance during data collection.

## Notes and references

- 1 C. D. Gutsche, *Acc. Chem. Res.*, 1983, **16**, 161–170.
- 2 C. D. Gutsche, B. Dhawan, K. H. No and R. Muthukrishnan, *J. Am. Chem. Soc.*, 1981, **103**, 3782–3792.
- 3 R. Muthukrishnan and C. D. Gutsche, *J. Org. Chem.*, 1979, **44**, 3962–3964.
- 4 S. J. Barrow, S. Kasera, M. J. Rowland, J. del Barrio and O. A. Scherman, *Chem. Rev.*, 2015, **115**, 12320–12406.
- 5 W. A. Freeman, W. L. Mock and N. Y. Shih, *J. Am. Chem. Soc.*, 1981, **103**, 7367–7368.
- 6 T. Ogoshi, S. Kanai, S. Fujinami, T. Yamagishi and Y. Nakamoto, *J. Am. Chem. Soc.*, 2008, **130**, 5022–5023.
- 7 S. E. Lewis, *Chem. Soc. Rev.*, 2015, **44**, 2221–2304.
- 8 R. Jasti, J. Bhattacharjee, J. B. Neaton and C. R. Bertozzi, *J. Am. Chem. Soc.*, 2008, **130**, 17646–17647.
- 9 X. Yan, T. R. Cook, P. Wang, F. Huang and P. J. Stang, *Nat. Chem.*, 2015, **7**, 342–348.
- 10 Y. Liu, W. Zhao, C. H. Chen and A. H. Flood, *Science*, 2019, **365**, 159–161.
- 11 M. Yamashina, Y. Tanaka, R. Lavendomme, T. K. Ronson, M. Pittelkow and J. R. Nitschke, *Nature*, 2019, **574**, 511–515.
- 12 Y. Ni, T. Y. Gopalakrishna, H. Phan, T. Kim, T. S. Heng, Y. Han, T. Tao, J. Ding, D. Kim and J. Wu, *Nat. Chem.*, 2020, **12**, 242–248.
- 13 L. Zhang, Y. Jin, G. H. Tao, Y. Gong, Y. Hu, L. He and W. Zhang, *Angew. Chem., Int. Ed.*, 2020, **59**, 20846–20851.
- 14 V. Abet, F. T. Szczypinski, M. A. Little, V. Santolini, C. D. Jones, R. Evans, C. Wilson, X. Wu, M. F. Thorne, M. J. Bennison, P. Cui, A. I. Cooper, K. E. Jelfs and A. G. Slater, *Angew. Chem., Int. Ed.*, 2020, **59**, 16755–16763.
- 15 X. Liu, Z. Shi, M. Xie, J. Xu, Z. Zhou, S. Jung, G. Cui, Y. Zuo, T. Li, C. Yu, Z. Liu and S. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 15080–15086.
- 16 H. Qu, X. Tang, X. Wang, Z. Li, Z. Huang, H. Zhang, Z. Tian and X. Cao, *Chem. Sci.*, 2018, **9**, 8814–8818.
- 17 A. G. Slater, M. A. Little, A. Pulido, S. Y. Chong, D. Holden, L. Chen, C. Morgan, X. Wu, G. Cheng, R. Clowes, M. E. Briggs, T. Hasell, K. E. Jelfs, G. M. Day and A. I. Cooper, *Nat. Chem.*, 2017, **9**, 17–25.
- 18 P.-E. Alexandre, W.-S. Zhang, F. Rominger, S. M. Elbert, R. R. Schröder and M. Mastalerz, *Angew. Chem., Int. Ed.*, 2020, **59**, 19675–19679.
- 19 X. Zheng, W. Zhu, C. Zhang, Y. Zhang, C. Zhong, H. Li, G. Xie, X. Wang and C. Yang, *J. Am. Chem. Soc.*, 2019, **141**, 4704–4710.
- 20 Y. Wang, H. Wu and J. F. Stoddart, *Acc. Chem. Res.*, 2021, **54**, 2027–2039.
- 21 P. Das, A. Kumar, P. Howlander and P. S. Mukherjee, *Chem. – Eur. J.*, 2017, **23**, 12565–12574.

- 22 C. J. Pugh, V. Santolini, R. L. Greenaway, M. A. Little, M. E. Briggs, K. E. Jelfs and A. I. Cooper, *Cryst. Growth Des.*, 2018, **18**, 2759–2764.
- 23 Z. Liu, G. Liu, Y. Wu, D. Cao, J. Sun, S. T. Schneebeli, M. S. Nassar, C. A. Mirkin and J. F. Stoddart, *J. Am. Chem. Soc.*, 2014, **136**, 16651–16660.
- 24 Z. Yang, C. Yu, J. Ding, L. Chen, H. Liu, Y. Ye, P. Li, J. Chen, K. J. Wu, Q. Y. Zhu, Y. Q. Zhao, X. Liu, X. Zhuang and S. Zhang, *Nat. Commun.*, 2021, **12**, 6124.
- 25 Y. D. Yang, X. L. Chen, J. L. Sessler and H. Y. Gong, *J. Am. Chem. Soc.*, 2021, **143**, 2315–2324.
- 26 Y. Lei, Q. Chen, P. Liu, L. Wang, H. Wang, B. Li, X. Lu, Z. Chen, Y. Pan, F. Huang and H. Li, *Angew. Chem., Int. Ed.*, 2021, **60**, 4705–4711.
- 27 A. Dey, S. Chand, L. O. Alimi, M. Ghosh, L. Cavallo and N. M. Khashab, *J. Am. Chem. Soc.*, 2020, **142**, 15823–15829.
- 28 T. Hasell, M. Schmidtman and A. I. Cooper, *J. Am. Chem. Soc.*, 2011, **133**, 14920–14923.
- 29 Y. Wang, J. Yang, Y. Gong, M. Fang, Z. Li and B. Z. Tang, *SmartMat*, 2020, **1**, e1006–e1014.
- 30 H. Qu, Z. Huang, X. Dong, X. Wang, X. Tang, Z. Li, W. Gao, H. Liu, R. Huang, Z. Zhao, H. Zhang, L. Yang, Z. Tian and X. Cao, *J. Am. Chem. Soc.*, 2020, **142**, 16223–16228.
- 31 J. Liang, B. Z. Tang and B. Liu, *Chem. Soc. Rev.*, 2015, **44**, 2798–2811.
- 32 J. Chen, L. Chen, Y. Wu, Y. Fang, F. Zeng, S. Wu and Y. Zhao, *Nat. Commun.*, 2021, **12**, 6870.
- 33 S. Cao, J. Shao, H. Wu, S. Song, M. T. D. Martino, I. A. B. Pijpers, H. Friedrich, L. K. E. A. Abdelmohsen, D. S. Williams and J. C. M. van Hest, *Nat. Commun.*, 2021, **12**, 2077.
- 34 Y. Li, X. Wu, B. Yang, X. Zhang, H. Li, A. Umar, N. F. Rooij, G. Zhou and Y. Wang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 37077–37083.
- 35 D. D. La, S. V. Bhosale, L. A. Jones and S. V. Bhosale, *ACS Appl. Mater. Interfaces*, 2018, **10**, 12189–12216.
- 36 S. N. Lei, H. Xiao, Y. Zeng, C. H. Tung, L. Z. Wu and H. Cong, *Angew. Chem., Int. Ed.*, 2020, **59**, 10059–10065.
- 37 X. Li, Z. Li and Y. W. Yang, *Adv. Mater.*, 2018, **30**, 1800177.
- 38 J. Roose, B. Z. Tang and K. S. Wong, *Small*, 2016, **12**, 6495–6512.
- 39 J. B. Xiong, H. T. Feng, J. P. Sun, W. Z. Xie, D. Yang, M. Liu and Y. S. Zheng, *J. Am. Chem. Soc.*, 2016, **138**, 11469–11472.
- 40 H. T. Feng, Y. X. Yuan, J. B. Xiong, Y. S. Zheng and B. Z. Tang, *Chem. Soc. Rev.*, 2018, **47**, 7452–7476.
- 41 L. Bian, Y. Liang and Z. Liu, *ACS Appl. Nano Mater.*, 2022, DOI: [10.1021/acsnm.2c01250](https://doi.org/10.1021/acsnm.2c01250).
- 42 M. Zhang, J. Guo, T. Liu, Z. He, M. Irfan, Z. Zhao and Z. Zeng, *J. Mater. Chem. C*, 2020, **8**, 14919–14924.
- 43 H. Duan, Y. Li, Q. Li, P. Wang, X. Liu, L. Cheng, Y. Yu and L. Cao, *Angew. Chem., Int. Ed.*, 2020, **59**, 10101–10110.
- 44 J. Jiao, Z. Li, Z. Qiao, X. Li, Y. Liu, J. Dong, J. Jiang and Y. Cui, *Nat. Commun.*, 2018, **9**, 4423–4430.
- 45 C. Zhang, Z. Wang, L. Tan, T. L. Zhai, S. Wang, B. Tan, Y. S. Zheng, X. L. Yang and H. B. Xu, *Angew. Chem., Int. Ed.*, 2015, **54**, 9244–9248.
- 46 Q. Huang, W. Li, Z. Mao, L. Qu, Y. Li, H. Zhang, T. Yu, Z. Yang, J. Zhao, Y. Zhang, M. P. Aldred and Z. Chi, *Nat. Commun.*, 2019, **10**, 3074–3081.
- 47 M. Li, S. Jiang, Z. Zhang, X. Q. Hao, X. Jiang, H. Yu, P. Wang, B. Xu, M. Wang and W. Tian, *CCS Chem.*, 2020, **2**, 337–348.
- 48 Y. Peng, L. Li, C. Zhu, B. Chen, M. Zhao, Z. Zhang, Z. Lai, X. Zhang, C. Tan, Y. Han, Y. Zhu and H. Zhang, *J. Am. Chem. Soc.*, 2020, **142**, 13162–13169.
- 49 H. Qu, Y. Wang, Z. Li, X. Wang, H. Fang, Z. Tian and X. Cao, *J. Am. Chem. Soc.*, 2017, **139**, 18142–18145.
- 50 K. Anzai, S. Kawamorita, N. Komiya and T. Naota, *Chem. Lett.*, 2017, **46**, 672–675.