

Cite this: *Nanoscale Adv.*, 2019, 1, 334

Heterostructure of two different 2D materials based on MoS₂ nanoflowers@rGO: an electrode material for sodium-ion capacitors†

Kiruthiga Ramakrishnan,^a Chandrasekaran Nithya ^{*a} and Ramasamy Karvembu ^b

Sodium ion capacitors are under extensive investigation as companionable pre-existing lithium ion batteries and sodium ion batteries. Finding a suitable host for sodium ion storage is still a major challenge. In this context, here we report a MoS₂ nanoflowers@rGO composite produced *via* a hydrothermal method followed by an ultra sonication process as a sodium ion symmetric hybrid supercapacitor. The structural and electrochemical performances of the electrode material were investigated to establish its applicability in sodium ion capacitors. The electrochemical performance was evaluated using metallic sodium in a half cell configuration which delivered a maximum specific capacitance of 226 F g⁻¹ at 0.03 A g⁻¹. When examined as a symmetric hybrid electrode (full cell) it delivered a maximum capacitance of 55 F g⁻¹ at 0.03 A g⁻¹. This combination may be a new gateway for upcoming research work which deals with sodium ion storage applications. The results confirmed that the as-synthesized MoS₂ nanoflowers@rGO heterostructure electrode exhibited notable electrochemical behaviour.

Received 25th July 2018
Accepted 4th September 2018

DOI: 10.1039/c8na00104a

rsc.li/nanoscale-advances

Introduction

Currently, extensive attention has been paid to energy storage and energy conversion, as a consequence of increasingly technology dependent human lives and advancement in the world economy. Batteries and supercapacitors are significant energy storage devices for hybrid electric vehicles and portable electronics.^{1,2} Among these, supercapacitors store electrical energy on the basis of charge accumulation on large surface area materials, known as electrical double layer capacitors (EDLCs), or through fast redox (faradaic) reactions, where they are called pseudocapacitors. Supercapacitors based on novel electrode nanomaterials have shown remarkable progress owing to their ultrafast charge–discharge rate, long cycle life and high power density. However, significant advancements are required to improve the energy density of supercapacitors. The energy and power density of supercapacitors are mainly governed by the elementary charge storage mechanism and the resultant kinetics at the electrode/electrolyte interface. Generally, the

performance of supercapacitors is basically dependent on the electrode materials.^{3–8}

As proficient energy storage devices, supercapacitors should be able to constrain active components. In contrast to batteries, supercapacitors are rich in power density but still have lower energy density than batteries.^{9,10} Hence, investigations are being carried out to enhance both energy and power density by combining battery and supercapacitor technologies through the smart combination of electrode materials.

Of these materials, sodium ion supercapacitors (NICs) are listed as one of the hotspots in the field of energy storage devices. The use of capacitive storage based on sodium ion systems is smart and cost-effective and they are competent substitutes for other systems.^{11,12} The properties of the materials used in the devices are essential for determining the performance of the supercapacitors.

Metal oxides have been extensively investigated as active materials for supercapacitors due to their high specific capacitance and ease of fabrication.¹³ Recently, metal nitrides, carbides and sulphides have arisen as new and promising electrode materials for high-performance supercapacitors. Among the metal sulphides, NiS, Co₉S₈, MoS₂, WS₂, and SnS₂ have been considered for energy storage applications of which MoS₂ may be of special interest.^{14–17} It has many key advantages like high theoretical capacity, good rate capability and good cyclability. Metal sulphides with structural features analogous to graphene have gained further attention recently on account of their distinctive structural, electronic, and electrochemical properties.^{18–22}

^aDepartment of Energy and Environment, National Institute of Technology, Tiruchirappalli – 620015, India

^bDepartment of Chemistry, National Institute of Technology, Tiruchirappalli – 620015, India. E-mail: nithyajcs@gmail.com

† Electronic supplementary information (ESI) available: XRD of GO and rGO, TG curves of MoS₂ and MoS₂@rGO composite, Raman spectrum of rGO, charge discharge curves of MoS₂@rGO composites, Nyquist plots of MoS₂ and MoS₂@rGO composite, electrochemical performance of pristine MoS₂ vs. Na/Na⁺ (half cell and full cell), charge discharge curve of rGO (full cell). HRTEM image and SAED pattern of MoS₂@rGO composite electrode after cycling. See DOI: 10.1039/c8na00104a



Moreover, MoS₂ can offer capacitive properties. It has a theoretical capacity higher than that of graphite and higher ionic conductivity compared to metal oxides. Hence, MoS₂ could be a better choice for sodium ion storage applications. The layered structure of MoS₂ has a tendency to restack due to its large surface energy correlated with weak van der Waals attraction. It can be assumed that this layered structure facilitates the appropriate insertion of foreign atoms and provides stability to the whole structure, which is beneficial for the electrochemical stability. Further, poor electrical conductivity impedes its performance in energy storage applications.^{23–25} This can be overcome by making composites with carbon matrixes which can offer enhanced electrical conductivity, mechanical strength and thermal stability. Herein, we have reported a sodium ion symmetric hybrid supercapacitor based on a MoS₂@rGO composite.

Molybdenum disulphide has a similar structure to reduced graphene oxide, with excellent physical and electrical properties. It has emerged as an attractive candidate to be mixed with reduced graphene oxide to form a composite with improved characteristics. The combination of MoS₂ with rGO is seen as a fundamental tactic for enhancing the electrochemical performance of active materials. The reduced graphene oxide will provide an efficient pathway for the diffusion of sodium ions and also firmly hold the active material during cycling. Due to its aforementioned properties, rGO can be exploited as an ideal support for graphene like MoS₂. Most importantly, the rGO matrix can not only effectively enhance the conductivity and stability of the active materials but can also significantly hamper the aggregation of MoS₂ sheets.^{26–30}

Results and discussion

Fig. 1 shows the XRD patterns of MoS₂ and the MoS₂@rGO composite. The XRD pattern of MoS₂ is indexed with a hexagonal structure with the space group *P6₃/mmc* (ICSD ref. no: 01-075-1539). The peaks at 14.12°, 33.60°, 39.59°, and 59.16° correspond to the (002), (100), (103) and (110) planes of MoS₂, respectively. The peak at 14.03° relates to the (002) plane,

confirming the hexagonal layered structure of MoS₂.³¹ The diffraction peaks of rGO do not appear in the XRD of the MoS₂@rGO composite, which confirms the lower content of rGO in the composite. The XRD pattern of rGO (as shown in Fig. S1†) consists of a broadened peak located at around 25.15°, corresponding to 002 diffraction of the graphitic layered structure as a result of GO reduction, with the shifting of the peak at $2\theta = 10.56^\circ$ attributable to disordered graphene layers with few structural defects.

Fig. S2† depicts the thermogravimetric curves of MoS₂ and the MoS₂@rGO composite. The minor weight loss region around 160 °C is due to absorbed water molecules. For MoS₂, the weight loss around 300 °C is mainly due to the oxidation of MoS₂ into MoO₃ and the remaining weight is 59.3% of the initial weight. In the composite, the weight remaining is 45.6%, which confirms that the composite contains 13.7% rGO.

Raman spectroscopy was employed here to evaluate the existence of rGO in the composite and the hexagonal layered structure of MoS₂. Fig. 2 shows the Raman spectrum of the MoS₂@rGO composite. The peaks appearing at 379.4 and 405.5 cm⁻¹ confirm the in-plane vibrational modes of the S–Mo–S bond. The energy difference between the two peaks of MoS₂ can reveal the number of layers of MoS₂. The obtained value of 26.1 cm⁻¹ confirmed that the MoS₂ contains few layers.³² Further, the D band (1341.6 cm⁻¹) and the G band (1570.4 cm⁻¹) reveal the presence of rGO in the composite. Fig. S3 (see ESI†) depicts the Raman spectrum of pure rGO. The characteristic D and G bands were observed at 1338 and 1593 cm⁻¹, respectively. The I_D/I_G value of rGO is 1.13, which results in more defective graphene layers in rGO.

The morphology of the as synthesized materials was analysed using field emission scanning electron microscopy (FESEM) and high resolution transmission electron microscopy (HRTEM). The image shown in Fig. 3a reveals the sheet- or leaf-like morphology of rGO. The flower-with-petals-like morphology of bare MoS₂ at two different magnifications is shown in Fig. 3b and c, which represent the uniformity of the MoS₂ particles. In the composite (Fig. 3d), the MoS₂ flowers are scattered and

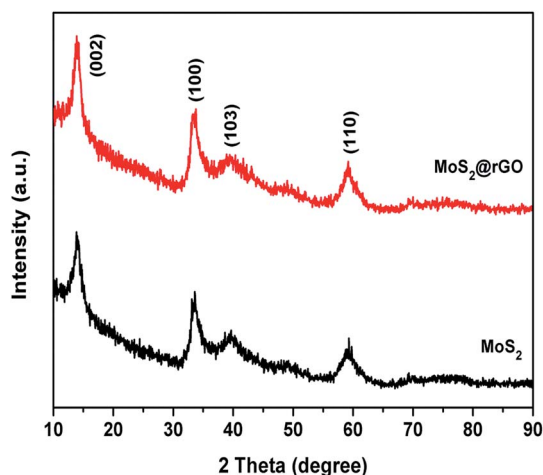


Fig. 1 XRD patterns of MoS₂ and MoS₂@rGO composite.

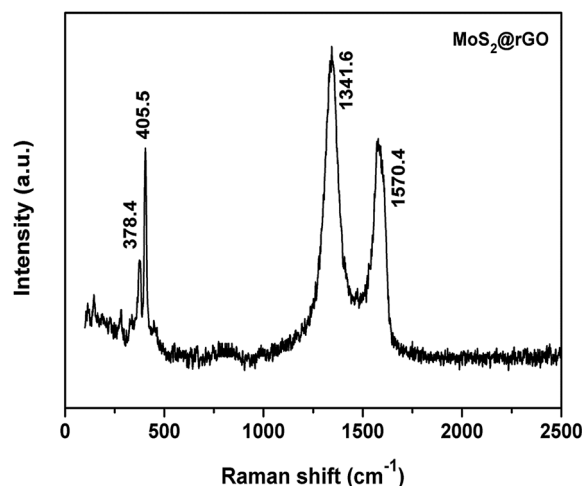


Fig. 2 Raman spectrum of MoS₂@rGO composite.





Fig. 3 FESEM images of (a) rGO, (b & c) MoS₂ at different magnifications and (d) MoS₂@rGO composite.

firmly held by the rGO sheets. HRTEM images of the samples are shown in Fig. 4. The image of rGO is in good agreement with the results obtained from the FESEM image. Fig. 4b and c

demonstrate the uniform array of MoS₂ nanoflowers at different magnifications. In the case of the composite, MoS₂ creases with the rGO sheets (Fig. 4d).



Fig. 4 HRTEM images of (a) rGO, (b & c) MoS₂ at different magnifications and (d) MoS₂@rGO composite.



results in the good electrochemical performance of MoS₂@rGO. The straight line in the low frequency region (Warburg region) corresponds to the sodium ion diffusion process as well as the ideal capacitive behaviour of the composite electrode. The diffusion coefficient (D) value of the MoS₂@rGO composite electrode was calculated using the following equation.^{34,35}

$$D = R^2 T^2 / 2 A^2 n^4 F^4 C^2 \sigma^2 \quad (1)$$

where R is the gas constant (J K⁻¹ mol⁻¹), T is the absolute temperature (K), n is the number of electrons transferred, A is the area of the electrode (cm²), C is concentration (mol cm⁻³), F (coulomb mol⁻¹) is the Faraday constant and σ is the coefficient of Warburg impedance, which is obtained from the extrapolation of the straight line from the semicircle to a real axis and is equal to ($R_s + R_{ct} - 2\sigma^2 C_{dl}$). R_s is the solution resistance in the bulk electrolyte, R_{ct} is the charge transfer resistance and C_{dl} is the double layer capacitance in the electrode–electrolyte interface. Teng *et al.*³⁶ calculated the diffusion coefficient for a sandwich-like graphene@MoS₂@C sheets (G@MS@C) electrode and found a value of 2.32×10^{-12} cm² s⁻¹. In our study, the calculated diffusion coefficients of pristine MoS₂ and the MoS₂@rGO composite are 11.31×10^{-12} and 8.12×10^{-10} cm² s⁻¹, respectively, which leads to good electrochemical performance in the MoS₂ nanoflowers@rGO composite. MoS₂ nanoflowers@rGO exhibits conductivity two orders of magnitude higher than that of the G@MS@C electrode. The improved conductivity is mainly due to the existence of a highly conductive rGO matrix in the composite.


So far, many efforts have been made to apply MoS₂ as an electrode in aqueous supercapacitors (as shown in Table S1†). Karade *et al.* prepared ultrathin MoS₂ nanoflakes *via* a chemical bath deposition method with a capacitance of 576 F g⁻¹ at 5 mV s⁻¹ in 0.5 M Na₂SO₄.³⁷ Ramadoss *et al.* reported mesoporous MoS₂ with a maximum capacitance of 376 and 403 F g⁻¹ at 1 mV s⁻¹ in 1 M Na₂SO₄ and 1 M KCl, respectively.³⁸ Ilanchezhian *et al.* synthesized MoS₂ nanospheres with a specific capacitance of 122 at 5 mV s⁻¹ in 1 M Na₂SO₄.³⁹ Soon *et al.* achieved a maximum capacitance of 100 F g⁻¹ at 1 mV s⁻¹ in 0.5 M H₂SO₄.⁴⁰ But the reports available for MoS₂ in non-aqueous electrolytes for sodium ion supercapacitors are few in number. Wang *et al.* constructed a Na-ion pseudocapacitor with a MoS₂/graphene composite which delivered a capacitance of 50 F g⁻¹ at 1.5 C in 1 M NaClO₄ (in PC + FEC) electrolyte.²⁸ Cook *et al.* examined the pseudocapacitive behaviour of mesoporous MoS₂ for sodium ion storage and reported a specific capacity of 118 mA h g⁻¹ at 1 mV s⁻¹ in a half cell configuration with 1 M NaClO₄ (in PC) electrolyte and concluded that MoS₂ is the ultimate candidate to host the larger alkali ions because its large van der Waals gap and nanoscale architecture can lead to charge storage *via* a pseudocapacitive mechanism.²⁷ In this work we used NaPF₆ (in EC + DEC) as the electrolyte and achieved a maximum capacitance of 226 F g⁻¹ in a half cell configuration.

The electrochemical performance of pristine MoS₂ (both half cell and full cell) is shown in Fig. S6.† Pristine MoS₂ delivered

a maximum capacitance of 119 and 24 F g⁻¹ at 0.03 A g⁻¹ in the half cell and the full cell configuration, respectively, with similar pseudocapacitive behaviour, which was confirmed by charge–discharge and CV studies. Further, 56% (half cell) and 23% (full cell) of the initial capacitance was observed after 2000 cycles. We also fabricated the capacitor without MoS₂ nanoflowers and investigated its electrochemical performance. The charge discharge profile of rGO (full cell) is shown in Fig. S7.† In the full cell configuration, it delivered a maximum capacitance of 22 F g⁻¹ at 0.03 A g⁻¹.

A further symmetric sodium ion capacitor (full cell configuration, Scheme 1) was fabricated in which two identical electrodes were used (MoS₂ nanoflowers@rGO composite). Galvanostatic charge–discharge measurements were carried out at various current densities as a function of time *vs.* voltage (Fig. 6a). The maximum specific capacitance achieved at a current density of 0.03 A g⁻¹ was 55 F g⁻¹, which decreased to only 6 F g⁻¹, even at a high current density of 4.02 A g⁻¹. A full cell has different electrochemical behaviour compared to that of a half cell. The reason may be attributed to the limited supply of reversible sodium in the case of the full cell. The initial coulombic efficiency of the full cell was 79%. The low coulombic efficiency may be assigned to the formation of a solid electrolyte interface during the initial charge–discharge process and may also be due to an irreversible intercalation reaction during the initial charge–discharge cycle.²⁸ For comparison, the symmetric sodium ion capacitors were assembled using rGO, pristine MoS₂ and MoS₂@rGO electrodes and delivered specific capacitances of 22, 24 and 55 F g⁻¹, respectively, at a current density of 0.03 A g⁻¹. The enhancement of the electrochemical performance of the MoS₂@rGO composite when compared to pristine MoS₂ is mainly due to the rGO network, which serves as a conductive matrix as well as contributing some capacity, which leads to the good electrochemical performance of the composite.

The specific capacitances at different applied current densities is plotted in Fig. 6b. The cycling stability of the electrode was evaluated at a current density of 0.1 A g⁻¹. After 2000 cycles, it retained 67% of the initial capacitance (Fig. 6c). Even after prolonged cycling, the flower-like morphology has been retained with some disorder, which may be due to the PVDF

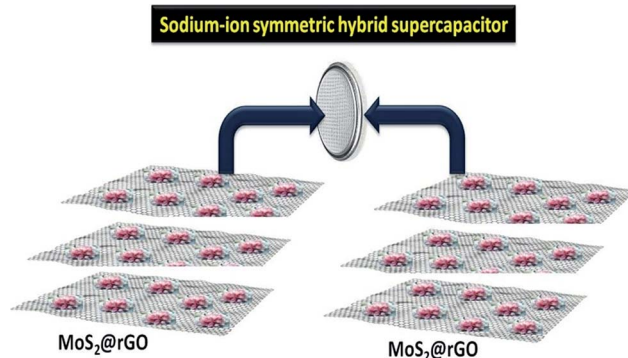

Scheme 1 Fabrication of a sodium-ion symmetric hybrid supercapacitor.



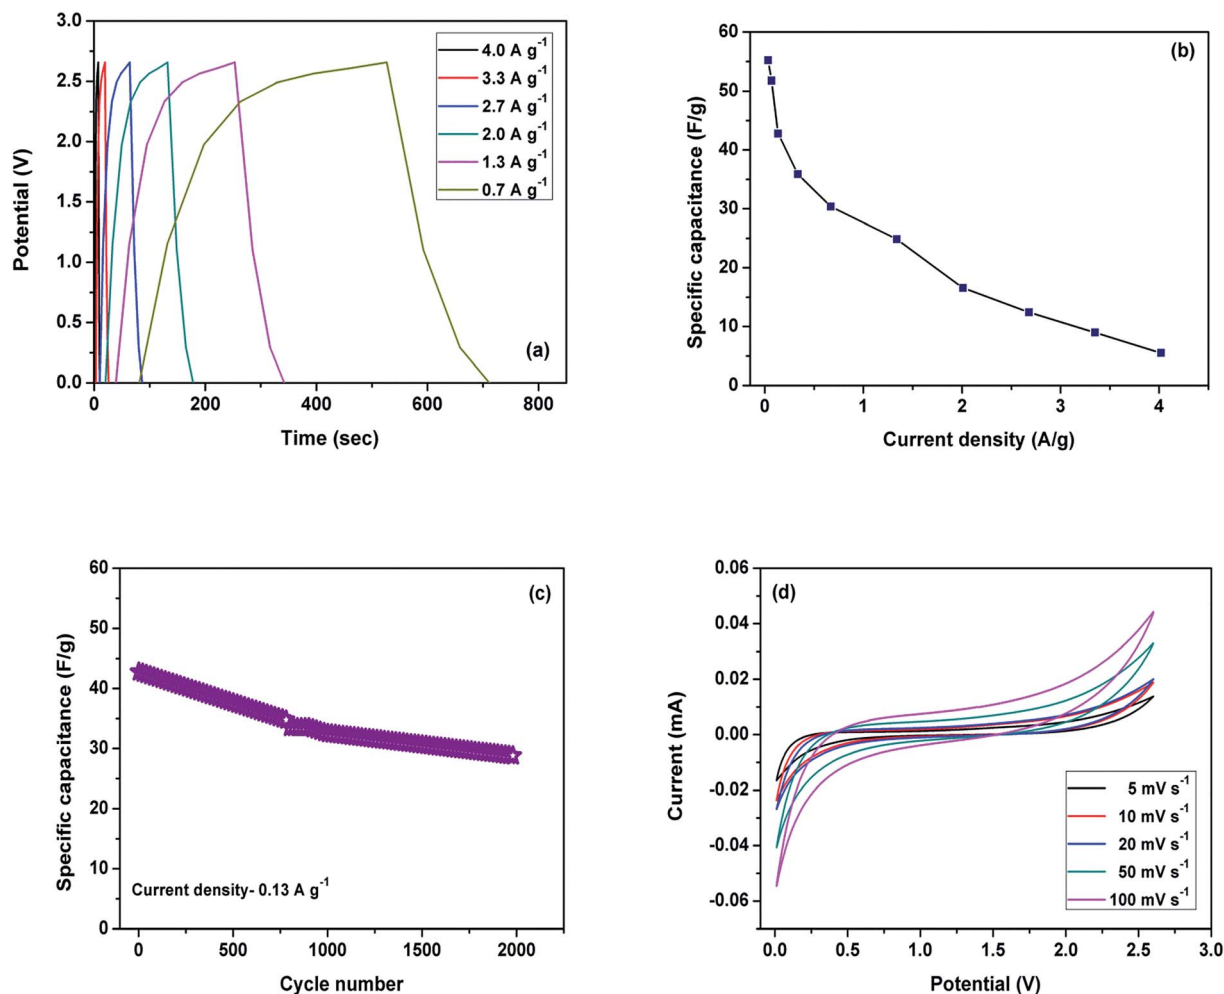


Fig. 6 Electrochemical performance of the symmetric hybrid device (full cell). (a) Galvanostatic charge–discharge curves; (b) specific capacitances at different current densities; (c) cycling performance; (d) cyclic voltammograms at different scan rates.

binder and conductive carbon used for the coating process, which was confirmed by HRTEM analysis (as shown in Fig. S8a & b†). The performance of the full cell was evaluated using CV studies at different scan rates, as shown in Fig. 6d. The CV curves were recorded at various scan rates (5–100 mV s⁻¹) in a potential window of 0.01 to 2.6 V. The CV curves are rectangular and identical in shape, indicating ideal capacitive characteristics and implying good reversibility of the electrode. The sodium ion symmetric hybrid supercapacitor consisting of the MoS₂@rGO composite delivers a maximum energy density of 52 W h kg⁻¹ and power density of 60 W kg⁻¹ at 0.03 A g⁻¹. The prominent electrochemical performance of the MoS₂@rGO composite in both the half cell and full cell configurations is mainly attributed to the rGO network, which can reduce the diffusion path length and boost ion transfer during the electrochemical reaction. Further, it induces the interfacial contact between the active particles, the electronic conductivity and the mechanical strength to hold the MoS₂ particles. Additionally, the structure of the MoS₂ nanoflower may provide easy access for electrolyte ions.

Experimental

Synthesis of MoS₂, rGO and the MoS₂@rGO nanocomposite

MoS₂ was synthesized using a hydrothermal method in which ammonium heptamolybdate and thiourea (mass ratio = 3 : 4) were dissolved separately in double distilled water.⁴¹ Then, both the solutions were mixed to form a homogeneous mixture under stirring. Afterwards, the mixture was sonicated for 2 h and transferred to a 200 ml Teflon-lined autoclave and heated at 180 °C for 28 h. The obtained black suspension was filtered and washed several times with water and dried in a hot air oven.

Graphene oxide (GO) was synthesized using a modified Hummers method.^{42,43} Reduced graphene oxide (rGO) was prepared by reduction of graphene oxide. In this process, the synthesized GO was dispersed in double distilled water and sonicated for 2 h. Then, sodium borohydride (NaBH₄) was added to it under sonication. After the addition of NaBH₄, it was stirred vigorously for 8 h. The precipitate that formed was filtered, dried at 60 °C for 48 h and ground well.

The molybdenum disulphide-reduced graphene oxide composite (MoS₂@rGO) was synthesized in a ratio of 85 : 15



from as synthesized MoS₂ and rGO. 0.15 g of rGO was dispersed in DI water under sonication for 1 h. 0.85 g of MoS₂ powder was added and allowed to sonicate for about 2 h. Further to this, the mixture was stirred for 24 h and the resulting black solid was separated by filtration and washed with DI water followed by ethanol to remove most residual ions. Finally it was dried at 80 °C for 24 h, and then the product was obtained as a fine powder after grinding. For comparison, composites with different compositions (80 : 20 and 90 : 10) were also prepared using the same procedure.

Structural characterization

The crystal structure of the material was evaluated using an X-ray diffractometer (XRD, Bruker D8) with Cu K α radiation ($\lambda = 1.5406 \text{ \AA}$), employing an operating voltage of 40 kV and a current of 20 mA between 10 and 90° at a scan rate of 2° min⁻¹. Thermogravimetric analysis was conducted (PerkinElmer/TGA4000) from room temperature to 900 °C at a heating rate of 20 °C min⁻¹ in an air atmosphere to obtain the proportion of rGO present in the composite. Morphology and particle size were characterized using a Field Emission Scanning Electron Microscope (FESEM, CARL ZEISS-Neon 40 microscope) and a High Resolution Transmission Electron Microscope (TEM, FEI Technai-20 G2 microscope). The Raman spectra of the samples were recorded at room temperature on a Renishaw InVia laser Raman microscope with a He-Ne laser ($\lambda = 633 \text{ nm}$).

Electrochemical characterization

The electrochemical behaviour of the synthesized material was analyzed using CR2032 coin type cells. The composite electrode was prepared by mixing 80 wt% active material with 10 wt% super P carbon (conductivity additive) and a 10 wt% PVDF (polyvinylidene fluoride) binder in NMP (*N*-methyl pyrrolidone) solvent. The obtained slurry was coated on Cu foil and used as a working electrode. The mass loadings of the active material for MoS₂ and MoS₂@rGO were 1.17 and 1.49 mg cm⁻², respectively. In the half cell configuration, sodium metal was used as a reference electrode. The electrolyte used was 0.75 M NaPF₆ in EC : DEC (1 : 1 v/v) mixture. The electrodes were separated by a polypropylene membrane (separator). Coin cells were assembled in an argon-filled glove box with an oxygen and water content of less than 1 ppm. To construct a symmetrical MoS₂@rGO based sodium ion capacitor, both sides used the same electrodes. The cyclic voltammograms were recorded using a Bio-Logic instrument (SP-240) with different scan rates from 5–100 mV s⁻¹ and electrochemical impedance spectra were measured using a Bio-Logic instrument (SP-250) in the frequency range between 100 kHz and 5 mHz. The cells were galvanostatically cycled using a battery tester (NEWARE) between 0.01 and 2.6 V. The specific capacitance of the single electrode was calculated according to the following equation.

$$C = 4I\Delta t/m\Delta V \quad (2)$$

where C (F g⁻¹) is the specific capacitance, I (A) is the current, ΔV (V) is the potential window during the discharge process, Δt

(s) is the discharge time and m (g) is the total mass of active materials in both the electrodes. The energy density and power density of the symmetric device were calculated using the following equations.

$$E = (1/2)C(\Delta V)^2 \quad (3)$$

$$P = E/t \quad (4)$$

where E (W h kg⁻¹) is the specific energy density, C (F g⁻¹) is the specific capacitance, ΔV (V) is the cell voltage, P (W kg⁻¹) is the specific power density and t (h) is the discharge time.⁴⁴

Conclusions

In summary, a MoS₂ nanoflower@rGO composite has been prepared using a simple and scalable hydrothermal method followed by an ultra sonication process. The better electrochemical performance of MoS₂ nanoflower@rGO is mainly owing to the sodium ion storage *via* the pseudocapacitive nature of MoS₂ and also the structural integrity, strong mechanical support and conductive pathway provided by the rGO network. MoS₂ nanoflowers@rGO delivers good electrochemical performance in terms of specific capacitance with various current densities and long-term cycling stability in half cell as well as in full cell configurations. The composite electrode delivered a maximum specific capacitance of 226 F g⁻¹ (in the half cell) and 55 F g⁻¹ (in the full cell) at 0.03 A g⁻¹. The sodium ion symmetric hybrid supercapacitor device made up of MoS₂ nanoflowers@rGO electrodes delivered a maximum energy density of 52 W h kg⁻¹ and a power density of 60 W kg⁻¹ at 0.03 A g⁻¹. The above mentioned observations and results offer ideas regarding a new pathway for a simple, cost effective MoS₂ nanoflowers@rGO composite electrode material for high performance energy storage devices which can fulfil future energy needs.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge the Department of Science and Technology (DST), India for support of this work under the DST-INSPIRE Faculty Award Project (Grant No. IFA-12-CH-42). One of the authors, Dr C. Nithya, wishes to thank the Department of Science and Technology (DST), India for the award of DST-Women Scientist.

Notes and references

- 1 M. Sevilla and R. Mokaya, *Energy Environ. Sci.*, 2014, 7, 1250–1280.
- 2 P. Yang and W. Mai, *Nano Energy*, 2014, 8, 274–290.
- 3 P. Simon, Y. Gogotsi and B. Dunn, *Science*, 2014, 343, 1210–1211.



- 4 B. Xu, H. Wang, Q. Zhu, N. Sun, B. Anasori, L. Hu, F. Wang, Y. Guan and Y. Gogotsi, *Energy Storage Mater.*, 2018, **12**, 128–136.
- 5 M. Saraf, R. Rajak and S. M. Mobin, *J. Mater. Chem. A*, 2016, **4**, 16432–16445.
- 6 A. Gigot, M. Fontana, M. Serrapede, M. Castellino, S. Bianco, M. Armandi, B. Bonelli, C. F. Pirri, E. Tresso and P. Rivolo, *ACS Appl. Mater. Interfaces*, 2016, **8**, 32842–32852.
- 7 E. Pomerantseva and Y. Gogotsi, *Nat. Energy*, 2017, **2**, 1–6.
- 8 M. Saraf, K. Natarajan and S. M. Mobin, *RSC Adv.*, 2017, **7**, 309–317.
- 9 H. Jiang, P. S. Lee and C. Li, *Energy Environ. Sci.*, 2013, **6**, 41–53.
- 10 J. Jiang, Y. Li, J. Liu, X. Huang, C. Yuan and X. W. D. Lou, *Adv. Mater.*, 2012, **24**, 5166–5180.
- 11 V. Aravindan, M. Ulaganathan and S. Madhavi, *J. Mater. Chem. A*, 2016, **4**, 7538–7548.
- 12 Z. Chen, V. Augustyn, X. Jia, Q. Xiao, B. Dunn and Y. Lu, *ACS Nano*, 2012, **6**, 4319–4327.
- 13 G. Wang, L. Zhang and J. Zhang, *Chem. Soc. Rev.*, 2012, **41**, 797–828.
- 14 F. Clerici, M. Fontana, S. Bianco, M. Serrapede, F. Perrucci, S. Ferrero, E. Tresso and A. Lamberti, *ACS Appl. Mater. Interfaces*, 2016, **8**, 10459–10465.
- 15 A. Lamberti, F. Clerici, M. Fontana and L. Scaltrito, *Adv. Energy Mater.*, 2016, **6**, 1–6.
- 16 A. Lamberti, *Mater. Sci. Semicond. Process.*, 2018, **73**, 106–110.
- 17 P. R. Jothi, R. R. Salunkhe, M. Pramanik, S. Kannan and Y. Yamauchi, *RSC Adv.*, 2016, **6**, 21246–21253.
- 18 M. Saraf, K. Natarajan, A. K. Saini and S. M. Mobin, *Dalton Trans.*, 2017, **46**, 15848–15858.
- 19 R. Zhou, C. J. Han and X. M. Wang, *J. Power Sources*, 2017, **352**, 99–110.
- 20 E. G. S. Firmiano, A. C. Rabelo, C. J. Dalmaschio, A. N. Pinheiro, E. C. Pereira, W. H. Schreiner and E. R. Leite, *Adv. Energy Mater.*, 2014, **4**, 1–8.
- 21 M. Saraf, K. Natarajan and S. M. Mobin, *ACS Appl. Mater. Interfaces*, 2018, **10**, 16588–16595.
- 22 Z. Chen, R. Wu, M. Liu, H. Wang, H. Xu, Y. Guo, Y. Song, F. Fang, X. Yu and D. Sun, *Adv. Funct. Mater.*, 2017, **27**(1702046), 1–13.
- 23 D. Su, S. Dou and G. Wang, *Chem. Commun.*, 2014, **50**, 4192–4195.
- 24 B. Qu, C. Ma, G. Ji, C. Xu, J. Xu, Y. S. Meng, T. Wang and J. Y. Lee, *Adv. Mater.*, 2014, **26**, 3854–3859.
- 25 J. Xiao, D. Choi, L. Cosimbescu, P. Koech, J. Liu and J. P. Lemmon, *Chem. Mater.*, 2010, **22**, 4522–4524.
- 26 X. Wang, Y. Li, Z. Guan, Z. Wang and L. Chen, *Chem.–Eur. J.*, 2015, **21**, 6465–6468.
- 27 J. B. Cook, H. S. Kim, Y. Yan, J. S. Ko, S. Robbennolt, B. Dunn and S. H. Tolbert, *Adv. Energy Mater.*, 2016, **6**(1501937), 1–12.
- 28 Y. X. Wang, S. L. Chou, D. Wexler, H. K. Liu and S. X. Dou, *Chem.–Eur. J.*, 2014, **20**, 9607–9612.
- 29 X. Xie, Z. Ao, D. Su, J. Zhang and G. Wang, *Adv. Funct. Mater.*, 2015, **25**, 1393–1403.
- 30 T. S. Sahu, Q. Li, J. Wu, V. P. Dravid and S. Mitra, *J. Mater. Chem. A*, 2017, **5**, 355–363.
- 31 P. Ramesh Kumar, Y. H. Jung and D. K. Kim, *RSC Adv.*, 2015, **5**, 79845–79851.
- 32 X. Xiong, W. Luo, X. Hu, C. Chen, L. Qie, D. Hou and Y. Huang, *Sci. Rep.*, 2015, **5**(9254), 1–6.
- 33 R. Kumuthini, R. Ramachandran, H. A. Therese and F. Wang, *J. Alloys Compd.*, 2017, **705**, 624–630.
- 34 R. Kiruthiga, C. Nithya, K. P. Bindhya, N. Kumar and S. Gopukumar, *ACS Sustainable Chem. Eng.*, 2017, **5**, 5090–5098.
- 35 R. Kiruthiga, C. Nithya, R. Karvembu and B. Venkata Rami Reddy, *Electrochim. Acta*, 2017, **256**, 221–231.
- 36 Y. Teng, H. Zhao, Z. Zhang, L. Zhao, Y. Zhang, Z. Li, Q. Xia, Z. Du and K. Swierczek, *Carbon*, 2017, **119**, 91–100.
- 37 S. S. Karade, D. P. Dubal and B. R. Sankapal, *RSC Adv.*, 2016, **6**, 39159–39165.
- 38 A. Ramadoss, T. Kim, G. S. Kim and S. J. Kim, *New J. Chem.*, 2014, **38**, 2379–2385.
- 39 P. Ilanchezhyan, G. Mohan Kumar and T. W. Kang, *J. Alloys Compd.*, 2015, **634**, 104–108.
- 40 J. M. Soon and K. P. Loh, *Electrochim. Solid-State Lett.*, 2007, **10**(11), A250–A254.
- 41 J. Li, Y. Hou, X. Gao, D. Guan, Y. Xie, J. Chen and C. Yuan, *Nano Energy*, 2015, **16**, 10–18.
- 42 X. Zhu, Y. Zhu, S. Murali, M. D. Stoller and R. S. Rouff, *ACS Nano*, 2011, **5**, 3333–3338.
- 43 W. S. Hummers and R. E. Offeman, *J. Am. Chem. Soc.*, 1958, **80**, 1339.
- 44 W. Qian, F. Sun, Y. Xu, L. Qiu, C. Liu, S. Wang and F. Yan, *Energy Environ. Sci.*, 2014, **7**, 379–386.

