



## Photocatalytic proton reduction with ruthenium and cobalt complexes immobilized on fumed reversed-phase silica†

C. Bachmann, B. Probst, M. Oberholzer, T. Fox and R. Alberto\*

Heterogeneous photocatalytic hydrogen production with a non-covalently immobilized molecular ruthenium based photosensitizer (PS) and a cobalt polypyridyl based water reducing catalyst (WRC) is reported. PS and WRC were derivatized with C<sub>18</sub>-alkyl chains and immobilized by adsorption on hydrophobic fumed silica. The resulting loaded support was suspended in water with anionic or cationic surfactants and subjected to heterogeneous photocatalytic H<sub>2</sub> production with ascorbate as sacrificial electron donor (SED). No leaching was observed under catalytic conditions, thus catalysis was truly heterogeneous. The catalytic performance of immobilized PS and WRC clearly exceeded that of homogeneous catalysis at low concentrations. At high concentration, diffusion and light limitation lead to lower reaction rates, but the same stability as for homogeneous reactions was still achieved. WRC concentration variations indicated a relatively high stability (up to 1300 H<sub>2</sub>/Co) and mobility of amphiphilic catalysts on the hydrophobic silica surface. Comparison of fumed silica with porous and non-porous silica showed, that a high BET surface area along with a good accessibility from the reaction media are crucial for catalytic performance. Mechanistic investigations by transient absorption spectroscopy displayed reductive quenching of excited PS by ascorbate followed by on particle electron transfer to WRC as reaction pathway. Particles with additional cationic surfactants exhibited a significantly higher catalytic performance as compared to anionic surfactants. Non-covalent anchoring of correspondingly derivatized WRCs or PSs to reversed-phase silica offers a rapid and versatile transition from homogeneous to heterogeneous molecular proton reduction.

Received 12th June 2015  
Accepted 8th October 2015

DOI: 10.1039/c5sc02124c

[www.rsc.org/chemicalscience](http://www.rsc.org/chemicalscience)

### Introduction

Photocatalytic water splitting into H<sub>2</sub> and O<sub>2</sub> with sun light (artificial photosynthesis) is a promising way to store solar energy in chemical bonds.<sup>1–3</sup> To drive the two half reactions, water oxidation and reduction, of this highly complex process with artificial molecular catalysts or (nano)materials remains a challenge. Approaches based on purely molecular components are complemented by strategies relying on materials.<sup>4–6</sup> Over the last decade, active, molecular water oxidizing and reducing catalysts (WOC, WRC) have been developed,<sup>2,7–15</sup> (and references therein) but light driven, full water splitting was mainly achieved with semiconductors or dye sensitized materials.<sup>5,16,17</sup> A fully homogeneous, molecular water splitting architecture is unlikely to exist since numerous back and cross electron transfers (shortcuts) between the O<sub>2</sub> and H<sub>2</sub> evolving half reactions (OER, HER) lead to self-inhibition.<sup>8</sup> Molecular (photo)catalysts for both reactions, immobilized on

nanomaterials in the same solution and connected through an electron relay, have been proposed as a viable route towards “one pot” water splitting, despite the disadvantage of getting mixtures of O<sub>2</sub> and H<sub>2</sub>.<sup>18</sup> Molecular catalysis on small solid phase particles is a topic of intensive research. Various methods, including covalent and non-covalent linking of molecular catalysts on polymeric or inorganic supports have been described for synthetic purposes.<sup>19–26</sup> Covalently bound catalysts are less prone to leaching, but specific synthetic strategies are required, which limit screening and reduce flexibility with respect to catalysts. Non-covalent immobilization – mostly by encapsulation or ionic, polar and apolar adsorption – is more convenient but weaker interactions lead to increased catalyst release and thus restricted applications.<sup>20,22–25</sup> Studies with particle bound, pure molecular catalysts for photocatalytic water oxidation or reduction are relatively rare. Particular examples rely on functional supports such as semiconductors, electrodes or quantum dots covered with molecular WOCs or WRCs.<sup>27–40</sup> Reisner and co-workers chemisorbed Co and Ru catalysts by polar interactions on TiO<sub>2</sub> and ZrO<sub>2</sub> particles. They observed “through particle” electron transfer (ET) for TiO<sub>2</sub> and “on particle” ET for ZrO<sub>2</sub>.<sup>41,42</sup> Meyer and co-workers recently reported a procedure to electropolymerize Ru based PS

Department of Chemistry, University of Zürich, Winterthurerstr. 190, CH-8057 Zürich, Switzerland. E-mail: ariel@chem.uzh.ch

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c5sc02124c

and WOC on  $\text{TiO}_2$  particles for photo- and electrocatalytically active electrodes.<sup>43</sup> Inspired by nature, König, Sun and co-workers embedded alkylated Co and Ru complexes in phospholipid membranes and observed a remarkable activity for both – oxidative and reductive – half reactions.<sup>44,45</sup> Anchoring in these membranes has the advantage of molecular mobility on the carrier material but the disadvantage of chemical and physical instability whereas the oxide materials required particular anchoring groups.

Silica particles, coated with hydrophobic, long alkyl chains, represent a combination between oxidic nanoparticles and membranes. These so-called reversed-phase materials as used in HPLC and preparative column chromatography are chemically and physically inert and interact strongly with molecules comprising pendent lipophilic groups. These strong, non-covalent interactions suppress leaching while keeping mobility on the alkylated surface intact. With minimal derivatization, essentially any catalyst or photosensitizer (or both) can be anchored on these materials. Hydrophobic interactions<sup>46</sup> were widely investigated for protein immobilization and synthetic purposes.<sup>22,23,47</sup> Adsorption by distinct alkyl-alkyl interactions are, however, rare; one particular example is based on fluorocarbon – derivatized catalysts adsorbed on fluorous reverse phase silica for Pd catalyzed cross coupling reactions.<sup>22</sup>

Acyclic cobalt complexes with poly-pyridyl ligands are a focus of recent research.<sup>14,48–56</sup> In our studies, the complex  $[\text{Co}^{\text{II}}\text{Br}(\text{appy})]\text{Br}$  **1** together with Re or Ru based PSs exhibited excellent proton reducing properties in homogeneous aqueous solution (Scheme 1).<sup>52,54</sup> A convenient way to immobilize these highly active WRCs alone or together with appropriate PSs on a robust support represents an important step towards a heterogenized architecture with molecular catalysts. Aforementioned non-covalent anchoring on solid phase materials *via* hydrophobic adsorption is straightforward and displacement of the components in aqueous media by protonation or competing (ionic or polar) species are greatly diminished.

We present in this study a flexible method to immobilize WRC **1** and  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$ , both derivatized with long alkyl chains, on hydrophobic fumed silica particles, a cheap, robust and commercially available high BET surface area material. As fumed silica is non-porous with high accessibility, good catalytic performance was expected from these composites compared to other silica based particles. For comparison, the catalysts were also anchored on porous silica with very high BET


surface area but low accessibility and on non-porous, spherical silica with high accessibility but low BET surface area. These nanocomposites are applied to heterogeneous, photocatalytic proton reduction and efficiency is compared to catalysis in homogeneous solution under equal conditions. The concept of anchoring catalysts on the hydrophobic surface of nano- or micromaterials is an excellent way of assessing the long-term performance of molecular systems.

## Results and discussion


### Synthesis and immobilization

WRC  $[\text{Co}^{\text{II}}\text{Br}(\text{appy})]\text{Br}$  **3** was synthesized in two steps; first, the hydroxy group of the basic polypyridyl ligand framework **2** (appy) was alkylated with octadecyl iodide, then WRC **3** was obtained by coordination to  $\text{Co}^{\text{II}}$  in 79% overall yield. The alkylated bpy ligand 4-methyl-4'-nonadecyl-2,2'-bipyridine ( $\text{C}_{19}\text{-bpy}$ , **4**) was obtained by deprotonation of 4,4'-dimethyl-2,2'-bipyridyl with  $\text{Li}[\text{N}(\text{isopropyl})_2]$  (LDA) followed by reaction with 1-bromoocadecane. The PS  $[\text{Ru}(\text{bpy})_2(\text{C}_{19}\text{-bpy})]^{2+}$  (**5**) finally was prepared from *cis*- $[\text{Ru}(\text{bpy})_2\text{Cl}_2]$  with **4** and subsequent counterion exchange with  $\text{NH}_4\text{PF}_6$  (Scheme 2).

Stirring hydrophilic fumed silica particles ( $\text{f-SiO}_2$ ) in  $\text{CH}_2\text{Cl}_2$  containing octadecyltrichlorosilane gave the hydrophobic fumed silica support  $\text{f-SiO}_2\text{-C}_{18}$ . The support was then loaded with 0.15  $\mu\text{mol}$  WRC and PS (**3** and **5**) per  $\text{m}^2$  BET surface area (equals 0.1 molecule per  $\text{nm}^2$ ,  $\sim 3$  mass% for fumed silica). To reduce particle agglomeration in aqueous solution and to increase the surface hydrophilicity, the surfactants sodium 4-dodecylbenzenesulfonate ( $\text{Na}[\text{C}_{12}\text{-PhSO}_3]$ , **6**) or *N,N,N*-trimethylhexadecyl ammonium acetate ( $[\text{C}_{16}\text{-NMe}_3]^+[\text{OAc}]$ , **7**, Scheme SI1†) were co-loaded. Stirring of respective methanol ( $\text{MeOH}$ ) solutions in the presence of  $\text{f-SiO}_2\text{-C}_{18}$ , followed by the addition of an aqueous electrolyte and subsequent  $\text{MeOH}$  evaporation gave

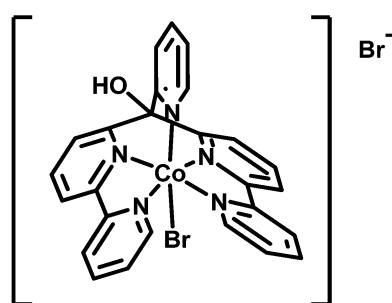

Scheme 1 Structure of water reducing catalyst  $[\text{Co}^{\text{II}}\text{Br}(\text{appy})]\text{Br}$  **1**.<sup>52,54</sup>

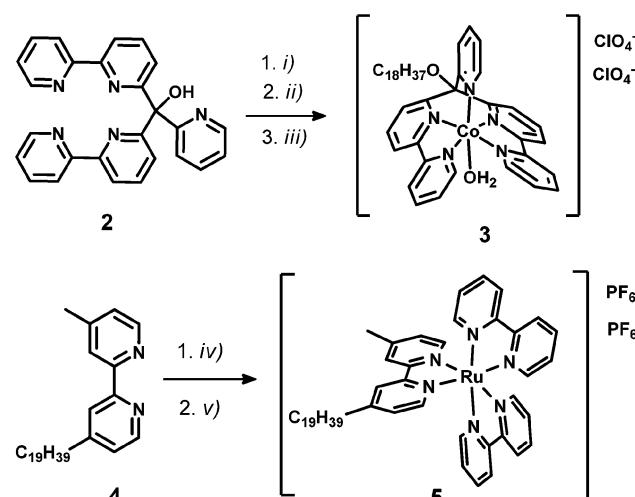

Scheme 2 Schematic representations of syntheses towards  $\text{C}_{18}/\text{C}_{19}$ -derivatized WRC and PS: (i)  $\text{NaH}$ ,  $\text{DMF}$ , rt, 45 min; (ii)  $\text{C}_{18}\text{H}_{37}\text{-I}$ , rt, 15 h; (iii)  $\text{Co}(\text{ClO}_4)_2$ ,  $\text{MeOH}$ , rt, 3 h; (iv)  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$ ,  $\text{EtOH}/\text{H}_2\text{O}$ ,  $100^{\circ}\text{C}$ , 24 h; (v)  $\text{NH}_4\text{PF}_6$ ,  $\text{H}_2\text{O}$ . Detailed synthetic procedures are given in the experimental part.



orange and luminescent silica particles which were isolated by centrifugation or filtration. Together with amphiphiles **6** and **7**, the formation of a mono-layer arrangement as shown by Ducker *et al.* for different ionic and non-ionic surfactants (Scheme 3) is expected.<sup>57</sup> Quantitative loading was assessed by HPLC analysis: the absence of a complex peak in the supernatant confirmed complete adsorption **3** and **5**, on f-SiO<sub>2</sub>-C<sub>18</sub>.

Particles loaded with complex **5** were examined by <sup>13</sup>C-CPMAS solid state NMR spectroscopy and compared to pure **5** as solid or in solution. The determined signals with loaded silica can clearly be assigned to adsorbed PS **5** (Fig. SI1†).

Transmission electron microscopy measurements (TEM, Fig. 1) of f-SiO<sub>2</sub> before and after silylation and loading with **5** clearly showed that the structure of fumed silica is not modified neither by silylation nor by double layer formation with the adsorbents. The particles still consist of *ca.* 20 nm spheres, which are condensed to chains and branches, forming particles of 200–500 nm in diameter. DLS measurements of these silica suspensions in water (at 1/1000 dilution) were in agreement with TEM results, and mean hydrodynamic diameters of several 100  $\mu\text{m}$  were found both for unloaded and loaded f-SiO<sub>2</sub>-C<sub>18</sub> (Table SI1†). A strong particle size dependency on the surfactant concentration was found. Low amounts of surfactant (<1 mM) did not fully suppress aggregation (Fig. SI2†) whereas too high amounts of amphiphiles (>10 mM) lead to release of adsorbed WRC or PS from the surface. Exposition and loading with 1–4 mM surfactant solutions were optimal for separating the particles to a homogeneous suspension.

Equally important as the surface hydrophilicity of the particles is the ionic strength of the electrolyte solution. Enhancing the ionic strength of solutions with suspended particles reduces the electrical double layer thickness around

the nanoparticles. Repulsive forces are thus reduced and aggregation is increased.<sup>58–60</sup> Indeed, addition of NaOTf electrolyte (0.1 M), as used in the photocatalysis experiments (*vide infra*), lead to a significantly increased particle size and size distribution ( $d = 0.5\text{--}5 \mu\text{m}$ , Table SI1†). Ascorbate buffer also leads to an increased hydrodynamic diameter, but the effect was clearly lower as compared to NaOTf. As DLS and TEM measurements demand high dilutions, suspensions at catalytic concentrations (*ca.* 7–8 mg per mL reaction solution) were studied by fluorescence microscopy (FM) using f-SiO<sub>2</sub>-C<sub>18</sub> loaded with PS **5**. Under these conditions, aggregates ranging from <1  $\mu\text{m}$  (detection limit) up to 50  $\mu\text{m}$  were observed (Fig. SI3†), possibly because of coagulation due to sedimentation in the measurement void between the two glass plates used for fluorescence microscopy. As shown in Fig. SI4,† dye **5** is evenly distributed in the aggregates, in line with the notation off small, dye decorated particles that aggregate.


### Photocatalysis

The loading processes on f-SiO<sub>2</sub>-C<sub>18</sub> particles as described before enable a convenient variation of the WRC/PS ratios, their absolute concentrations and the nature of the surfactants, respectively. WRC **3** and PS **5** were bound to the particles and amphiphile **7** was added to increase wettability. The photocatalytic H<sub>2</sub> evolution experiments were performed in 1 M ascorbic acid/ascorbate buffer (H<sub>2</sub>asc/H<sub>asc</sub><sup>–</sup>, pH = 4) as SED and with 0.1 M NaOTf as inert electrolyte. PS and WRC concentrations in these experiments are defined as the total amount (in mol) of immobilized complex, grafted on the support per catalysis solution volume (10 mL).

The suspensions were irradiated with a 453 nm LED and H<sub>2</sub> evolution continuously measured by automated GC as described earlier.<sup>52</sup> To make sure that **3** (WRC) or **5** (PS) did not leach from the supports and homogeneous catalysis was observed in fact, the particles were filtered from the suspension after preparation and the residual (colourless) solution irradiated separately (green line in Fig. 2). No H<sub>2</sub> evolution was observed, supporting retention of WRC and PS on the particles. However, since cobalt polypyridyl complexes are active catalysts already at low concentrations,<sup>52–54</sup> even minute leaching of WRC **3** would result in photocatalysis in the presence of significant amounts of PS **5**. To fully exclude this possibility, we added 500  $\mu\text{M}$  [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> to the separated solution and continued irradiation (2<sup>nd</sup> green arrow in Fig. 2). No increased photocatalytic activity was observed as compared to the blank experiment with no WRC and 500  $\mu\text{M}$  [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> only. This conclusively confirmed heterogeneous catalysis on the particles and not from WRC or PS or both eventually released into solution.

### Heterogeneous vs. homogeneous photocatalysis

Immobilised molecular catalysts give rise to high local concentrations on their respective support in heterogeneous catalysis, whereas in homogeneous catalysis the distribution in solution is even, but concentrations are low. Therefore, it was of interest to compare these two “reversed” situations; activity of

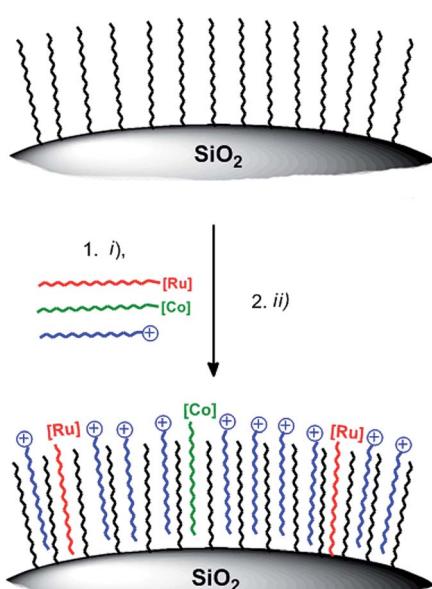

Scheme 3 Schematic illustration of WRC and PS adsorption on hydrophobic silica. (i) **3**, **5**, **7** (or **6**), MeOH, rt, 30 min (ii) 0.1 M NaOTf electrolyte, MeOH evaporation. Detailed synthetic procedures are given in the experimental part.



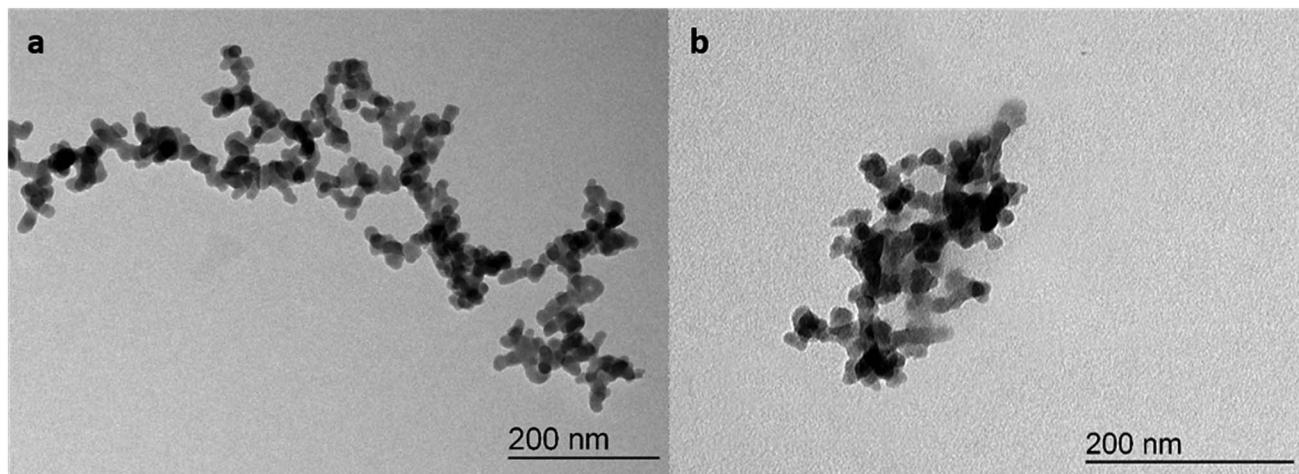


Fig. 1 Representative TEM micrograph of hydrophilic fumed silica without (a) and hydrophobic fumed silica with adsorbed PS 5 from a diluted aqueous suspension with 7 as surfactant (b).

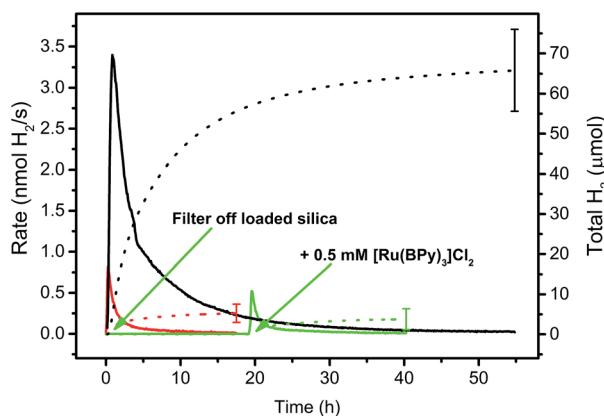


Fig. 2 Hydrogen evolution rate courses (solid lines) and total amounts of  $\text{H}_2$  (dotted lines) in 1 M ascorbate buffer (pH 4) with 0.1 M NaOTf. Black: 20  $\mu\text{M}$  3 and 200  $\mu\text{M}$  5 adsorbed on hydrophobic fumed silica with 300  $\mu\text{M}$   $[\text{C}_{16}\text{-NMe}_3]\text{OAc}$  (7) as surfactant. Green: same as black, but loaded silica was filtered off and the residual solution irradiated, then 0.5 mM  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$  was added and irradiation continued (green arrows). Red: 0.5 mM  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$ , no WRC. See Table S13.†

PS 5 and WRC 3, immobilized on  $\text{f-SiO}_2\text{-C}_{18}$  and  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$  and 1 in solution, assuming that the alkyl chains in 5 and 3 would not lead to significant activity differences with the latter PS and WRC. Fig. 3 and Table 1 show rates and amounts of  $\text{H}_2$  at different (WRC and PS) concentrations. For the heterogeneous reactions, the amount of  $\text{f-SiO}_2\text{-C}_{18}$  was reduced in order to keep the loading densities of 5 and 3 constant. At low catalysts concentrations ( $<20 \mu\text{M}$  PS and  $1 \mu\text{M}$  WRC), immobilized complexes 5 and 3 exceed the performance of  $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$  and 1 by far (Fig. 3 and Table 1). Apparently, electron transfer from reduced PS to  $\text{Co}^{\text{II}}$  becomes rate limiting in solution at low PS and WRC concentrations.  $\text{PS}^-$  is known to be unstable under aqueous conditions,<sup>61</sup> therefore at low concentration of 1, PS decomposition dominates and reaction rates and turnovers drop drastically. In heterogeneous catalysis, the local concentrations on the support silica remain constant and hence

catalytic activity of immobilized 5 and 3 is retained even at very low concentrations. This trend is shown in Fig. 3. At 20/1  $\mu\text{M}$  PS/WRC, the immobilized system produces  $\sim 3.5 \mu\text{mol H}_2$ , the homogeneous reaction  $\sim 1.5 \mu\text{mol}$ . At 10/0.5, this ratio becomes larger with  $\sim 1.5 \mu\text{mol}$  vs.  $\sim 0.25 \mu\text{mol}$ . At lowest concentrations, activity for the homogeneous catalysis is essentially lost, whereas the heterogeneous system remains active. We note a constant TOF in the heterogeneous system at  $[3] \leq 1 \mu\text{M}$  (see Table 1), indicating that electron transfer between PS and WRC is not rate limiting, unlike in the homogenous system. At catalyst concentrations  $\geq 100 \mu\text{M}$  PS and  $5 \mu\text{M}$  WRC, comparable total amounts of  $\text{H}_2$  were observed for both – homo- and heterogeneous catalysis (Table 1). Hence, the stability of

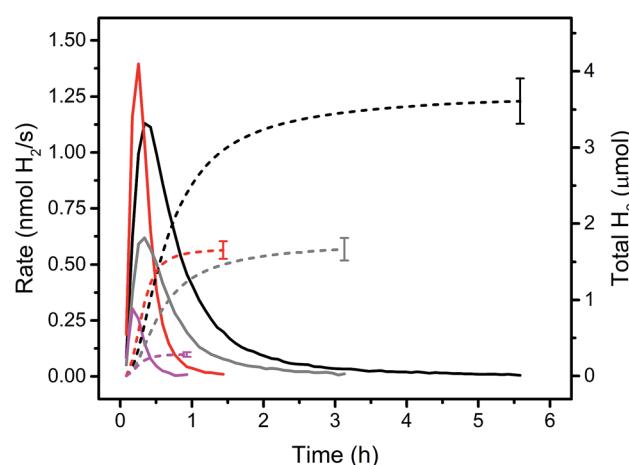


Fig. 3 Rates (solid lines) and amounts of  $\text{H}_2$  (dashed lines) for homo- and heterogeneous photocatalytic reactions in 1 M ascorbate buffer (pH 4) with 0.1 M NaOTf. Black: 20  $\mu\text{M}$  PS 5 and 1  $\mu\text{M}$  WRC 3 immobilized on  $\text{f-SiO}_2\text{-C}_{18}$  with 300  $\mu\text{M}$  7. Red: 20  $\mu\text{M}$   $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$  and 1  $\mu\text{M}$  1. Grey: 10  $\mu\text{M}$  PS 5 and 0.5  $\mu\text{M}$  WRC 3 immobilized on  $\text{f-SiO}_2\text{-C}_{18}$  with 150  $\mu\text{M}$  7. Magenta: 10  $\mu\text{M}$   $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$  and 0.5  $\mu\text{M}$  1. Detailed values are shown in Table 1.



**Table 1** Summarized results of homogeneous and heterogeneous photocatalytic  $H_2$  production in 10 mL aqueous 1 M ascorbate buffer (pH 4) with 0.1 M NaOTf. **3** and **5** immobilized on f-SiO<sub>2</sub>-C<sub>18</sub>, 15  $\mu$ M surfactant **7** per  $\mu$ M **5** and 0.1 M NaOTf. *Italic* font: homogeneously dissolved [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> and **1**. Rate courses and produced hydrogen of 20/1 and 10/0.5  $\mu$ M PS/WRC are depicted in Fig. 3

| [PS]/[WRC]<br>( $\mu$ M) | Max rate<br>(nmol $H_2$ /s)        | Total $H_2$<br>( $\mu$ mol)       | TON <sub>Co</sub><br>( $H_2$ /Co) |
|--------------------------|------------------------------------|-----------------------------------|-----------------------------------|
| <b>200/10</b>            | <b><math>3.9 \pm 0.3</math></b>    | <b><math>79 \pm 8</math></b>      | <b><math>790 \pm 80</math></b>    |
| <i>200/10</i>            | <i><math>12.0 \pm 0.75</math></i>  | <i><math>59 \pm 4</math></i>      | <i><math>590 \pm 40</math></i>    |
| <b>100/5</b>             | <b><math>2.85 \pm 0.2</math></b>   | <b><math>31.3 \pm 2.5</math></b>  | <b><math>626 \pm 50</math></b>    |
| <i>100/5</i>             | <i><math>11.4 \pm 0.7</math></i>   | <i><math>29.5 \pm 1.8</math></i>  | <i><math>590 \pm 36</math></i>    |
| <b>20/1</b>              | <b><math>1.11 \pm 0.07</math></b>  | <b><math>3.65 \pm 0.35</math></b> | <b><math>365 \pm 35</math></b>    |
| <i>20/1</i>              | <i><math>1.38 \pm 0.08</math></i>  | <i><math>1.65 \pm 0.14</math></i> | <i><math>165 \pm 14</math></i>    |
| <b>10/0.5</b>            | <b><math>0.62 \pm 0.04</math></b>  | <b><math>1.7 \pm 0.2</math></b>   | <b><math>340 \pm 40</math></b>    |
| <i>10/0.5</i>            | <i><math>0.30 \pm 0.02</math></i>  | <i><math>0.28 \pm 0.03</math></i> | <i><math>56 \pm 6</math></i>      |
| <b>2/0.1</b>             | <b><math>0.09 \pm 0.009</math></b> | <b><math>0.20 \pm 0.04</math></b> | <b><math>200 \pm 40</math></b>    |
| <i>2/0.1</i>             | <i>&lt;0.01</i>                    | —                                 | —                                 |


immobilized WRC **3** and PS **5** are similar to their homogeneous analogues.

However, homogeneous catalysis exhibited 3–4 fold higher  $H_2$  rates (Table 1). Presumably, two effects are responsible; (i) light is more uniformly absorbed in homogeneous solution and therefore more PS activated and (ii) reductive quenching of excited PS ( $Ru^*$ ) is significantly slower in heterogeneous catalysis as ascorbate diffusion to silica is limiting. Consequently, in this concentration range, distinctly higher  $H_2$  evolution rates were achieved with [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> and **1**. Apart from these limitations, immobilization does not adversely affect the catalyst performance since TONs for both systems are about identical (Table 1 and Fig. 3).

### Concentration dependencies

Complex **1** is a highly active WRC which achieves TON<sub>Co</sub> as high as 30 000  $H_2$ /Co, when back electron transfer is inhibited by the regeneration of DHA with tris-(2-carboxyethyl) phosphine (TCEP).<sup>52</sup> Catalytic performance as a function of the WRC concentration provides insights in process limitations. We therefore varied systematically the concentration of WRC **3**, while keeping PS **5** and all other parameters constant. If mobility's of **3** and **5** on f-SiO<sub>2</sub>-C<sub>18</sub> were low, WRC "dilution" will entail a linear decrease in rates with concentrations. Two distinct domains can be seen in Fig. 4: a constant  $H_2$  evolution rate, accompanied by a decrease in TON<sub>Co</sub> between 5 and 20  $\mu$ M WRC and a linear decrease in rate, accompanied by constant TON<sub>Co</sub> below [WRC] = 5  $\mu$ M.

In the first domain, as for homogenous catalysis, we assume the PS (**5**) cycle becomes rate limiting (number of photons, diffusion of ascorbate, quench yield). Although [Ru(bpy)<sub>3</sub>]<sup>2+</sup> is known to undergo rapid electron self-exchange reactions ( $PS + PS^- \leftrightarrow PS^- + PS$ ) at an estimated rate of  $\sim 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ,<sup>62</sup> the mean Ru–Ru distance under these conditions ( $\sim 3\text{--}4 \text{ nm}$  at  $0.15 \mu\text{mol m}^{-2}$ ) is too large for efficient electron hopping to the WRC, if catalysts were not mobile. We thus conclude that **3** and **5** remain mobile on hydrophobic silica which enables rapid

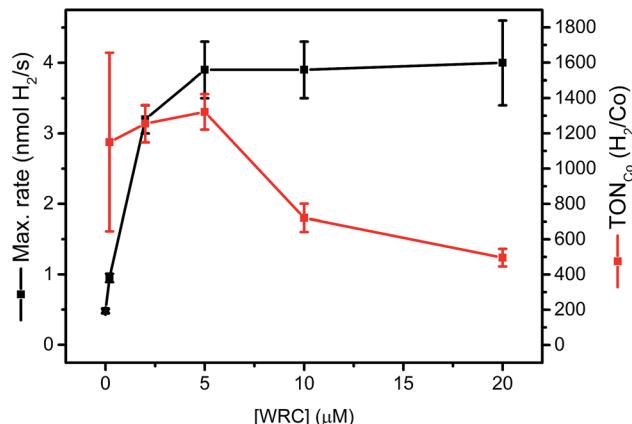

**Fig. 4** [WRC] dependency study with 200  $\mu$ M PS **5** and varying amounts of WRC **3** (0, 0.2, 2, 5, 10 and 20  $\mu$ M) adsorbed on f-SiO<sub>2</sub>-C<sub>18</sub> in 1 M ascorbate buffer, 0.1 M NaOTf and 300  $\mu$ M [C<sub>16</sub>-NMe<sub>3</sub>][OAc] (**7**) as surfactant. The amount of  $H_2$  from the blank experiment (no WRC) was subtracted at each concentration and the corresponding TONs in Co ( $H_2$ /Co) calculated (Table SI6†).

dynamic reorganization. The surface can be considered as a two dimensional liquid in interfacial contact with an aqueous solution. König and co-workers observed a similar mobility for complexes embedded into membranes.<sup>45</sup> The similar amounts of  $H_2$  obtained in the first domain (Table SI6†) also indicate PS degradation. A recycling experiment at high [WRC] further corroborated this hypothesis: replacing the catalysis medium by fresh ascorbic acid buffer solution after 20 h and 30 h of irradiation gave significantly increased reaction rates, whereas the total amount of evolved  $H_2$  was similar compared to other reactions with high [WRC] (Fig. S19 and Table SI6†). Consequently, catalysis is slowed down by DHA accumulation, but PS bleaching limits the stability.

In the second domain, below 5  $\mu$ M [WRC], we assume that the WRC cycle limits the rate. In contrast to the homogeneous reaction, TON<sub>Co</sub> did not increase in this domain, but remained constant (1300  $H_2$ /Co). As the stability of **3** is expected to be similar to **1** ( $>30\,000 \text{ } H_2/\text{Co}$  (ref. 52)) we hypothesize mobility limitation in the second domain: since reduced PS is unstable under aqueous conditions,<sup>61</sup> turnovers are limited if electron transfer to **3** ( $5^- + 3 \rightarrow 5 + 3^-$ ) becomes too slow at low [WRC]. Thus only reduced PS within a maximal distance of a WRC molecule can deliver its reduction equivalents, whereas those that are too far away will decompose.

Variation of the surface concentration of **3** and **5** (5 resp. 100  $\mu$ M) on varying amounts of f-SiO<sub>2</sub>-C<sub>18</sub> (0.02–0.27 molecules per  $\text{nm}^2$ ) gave a decrease of catalysis rate at low loading, whereas constant rates were observed above (Table SI4†).

Maximal  $H_2$  evolution rates and total amounts of evolved  $H_2$  at different concentrations of surfactants **6** (anionic) and **7** (cationic) are shown in Fig. 5. Both, maximal  $H_2$  evolution rates and total  $H_2$  amounts increased distinctly with decreasing concentrations of anionic surfactant **6** and otherwise identical conditions. Cationic surfactant **7**, on the other hand, gave higher catalytic activity and stability in the concentration range accessible for catalysis. Experiments using surfactants **6** and **7**



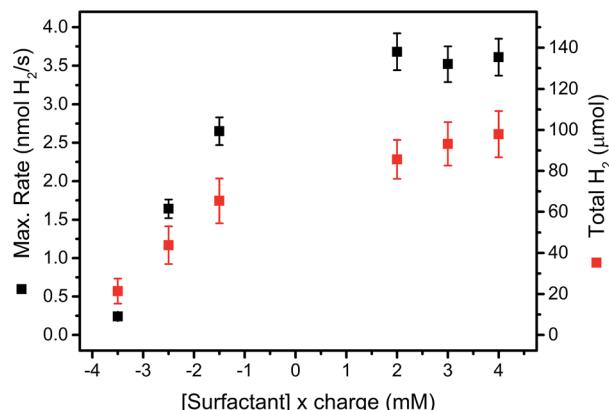


Fig. 5 Maximal  $\text{H}_2$  evolution rates (black squares, left scale) and total amounts of evolved  $\text{H}_2$  (red squares, right scale) in 1 M ascorbate buffer (pH 4) with 0.1 M NaOTf and 200  $\mu\text{M}$  PS 5 and 20  $\mu\text{M}$  WRC 3 immobilized on f-SiO<sub>2</sub>-C<sub>18</sub> at different surfactant concentrations (mM) multiplied by their charge (negative: Na[C<sub>12</sub>-PhSO<sub>3</sub>], 6; positive: [C<sub>16</sub>-NMe<sub>3</sub>]OAc, 7). Results are summarized in Table S15† and the structures of 6 and 7 depicted in Scheme S11.†

in a homogenous system gave no significant effect on the rate of photocatalysis (Table S12†). Electrostatic surface repulsion is thus a likely explanation in the immobilized system, as negatively charged ascorbate is attracted by a support surface covered with cationic 7, whereas diffusion of ascorbate onto silica is impeded by negatively charged 6. Thus reductive quenching of excited PS (Ru\*) becomes slower which entails a decreased reaction rate. In parallel, electron back transfer to the continuously formed, neutral DHA is reduced which results in more  $\text{H}_2$  with the cationic surfactant 7. Cationic surfactants are therefore superior to anionic counterparts in heterogeneous photocatalytic  $\text{H}_2$  production.

### Different silica supports

A high BET surface area, accessible for light and reaction components is crucial for catalytic activity. To support this hypothesis, we compared the performance of WRC 3 and PS 5 immobilized on three silica-based supports with different BET surface areas and accessibilities, but with similar particle diameters. Commercially available C<sub>18</sub>-silica ( $d = 40\text{--}70\ \mu\text{m}$ ) as used in reverse phase column chromatography is highly porous (pore size: 7 nm; pore volume: 0.7–0.9  $\text{cm}^3\ \text{g}^{-1}$ ) and has a very large BET surface area (480  $\text{m}^2\ \text{g}^{-1}$ ). Catalysts adsorbed in the pores might show altered kinetics (local accumulation of oxidised ascorbate, inhibition), and catalytic activity should therefore be low. Calcination of porous silica ( $d = 10\ \mu\text{m}$ ) at 1100 °C followed by C<sub>18</sub>-grafting, gives spherical, non-porous hydrophobic silica ( $d = 7\text{--}9\ \mu\text{m}$ , Scheme S15†) with a good accessibility but low BET surface area (ca. 0.5  $\text{m}^2\ \text{g}^{-1}$ , see Experimental part). These two silica based supports were compared to f-SiO<sub>2</sub>-C<sub>18</sub>, which is non-porous but consists of small silica chains and branches, aggregated to larger particles ( $d = 0.2\text{--}50\ \mu\text{m}$ , Fig. S13†) with a high BET surface area (200  $\text{m}^2\ \text{g}^{-1}$ ). Thus, fumed silica combines both advantages of porous and non-porous silica; a high BET surface area and good

accessibility. As expected, porous silica showed an even distribution of PS through the whole particle – similarly to f-SiO<sub>2</sub>-C<sub>18</sub> aggregates – whereas for non-porous silica PS was only observed on the particle surface (Fig. S15–S18†).  $\text{H}_2$  evolution rates and total amounts of  $\text{H}_2$  with 3 and 5 immobilized in these three supports are depicted in Fig. 6. Under comparable conditions, catalysts grafted to fumed silica exhibited a 10 times higher activity and the double amount of  $\text{H}_2$  in half the time as compared to porous silica (Fig. 6). Not all sites in porous silica are equally accessible to ascorbate and protons, and high local concentrations of DHA might inhibit catalysis. Consequently, only a fraction of the immobilized PS contributes to catalysis and lower rates are the result. Accessibility is thus an important factor, and a high BET surface area alone is not sufficient. A direct comparison to non-porous silica is difficult. Only small amounts of catalysts (30–40 times less) can be grafted as non-porous silica has only a very low BET surface area (ca. 0.5  $\text{m}^2\ \text{g}^{-1}$ ). Yet, 3 and 5 exhibited a 2–3 times higher maximal  $\text{H}_2$  evolution rate on non-porous compared to porous silica albeit  $\text{H}_2$  evolution ceased quickly due to low amounts of catalysts (Fig. 6). These results corroborate the importance of a high BET surface area and non-porosity as an essential base for efficient photocatalysis. Large quantities of well accessible catalysts can be adsorbed to maintain  $\text{H}_2$  formation over a long period, and high reaction rates are achieved through good accessibilities. Fumed silica is an excellent and cheap support for heterogeneous catalysis with immobilized molecular complexes.

### Mechanisms

For obtaining a closer insight into the mechanism of  $\text{H}_2$  formation and electron transfer in particular, we performed transient absorption spectroscopy of unsupported catalysts [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> and 1. There are two possible pathways; excited PS\* is reductively quenched by H<sub>asc</sub><sup>-</sup> followed by electron transfer to 1 and subsequent proton reduction (Scheme 4; 1–4.)


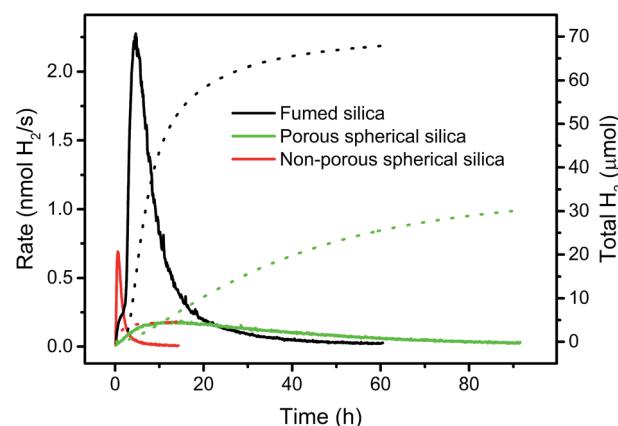


Fig. 6 Comparison of rates (solid lines, left scale) and  $\text{H}_2$  amounts (dotted lines, right scale) with WRC 3 and PS 5 immobilized on different types of hydrophobic silica in 1 M ascorbate buffer (pH = 4, 0.1 M NaOTf). Black: 200  $\mu\text{M}$  PS 5 and 40  $\mu\text{M}$  WRC 3 on f-SiO<sub>2</sub>-C<sub>18</sub> with 2.5 mM 6. Red: 4.8  $\mu\text{M}$  5 and 1  $\mu\text{M}$  3 on non-porous spherical silica with 100  $\mu\text{M}$  6. Green: 200  $\mu\text{M}$  5 and 40  $\mu\text{M}$  3 on porous silica with 2.5 mM 6.

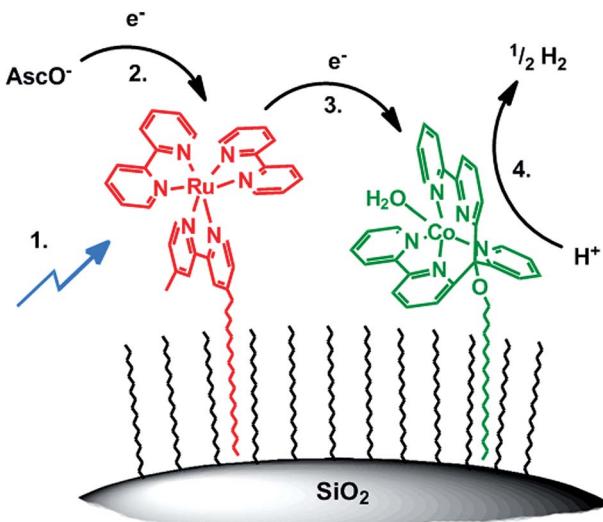

**Scheme 4** Proposed reaction mechanism of photocatalytic  $H_2$  production on hydrophobic silica: (1) photoexcitation of  $5 \rightarrow 5^*$ ; (2) reductive quenching of  $5^* \rightarrow 5^-$ ; (3) electron transfer  $5^- \rightarrow 3$ ; (4)  $H^+$  reduction by  $3^-$ .

or oxidative quenching of  $Ru^*$  by **1** followed by reduction of oxidized  $[Ru(bpy)_3]^{2+}$  ( $Ru^{III}$ ) with  $H_{asc}^-$ . Although less likely, the second pathway cannot be excluded “*a priori*” since on the particle, **3** and **5** are in intimate vicinity. Transient absorption spectroscopy in water with  $[CoBr(appy)]Br$  (**1**) and  $[Ru(bpy)_3]Cl_2$  did, however, not show any detectable formation of  $Ru^{III}$  or  $Co^I$  species, but non-productive quenching, most likely by energy transfer from  $PS^*$  to **1** with  $k_q = 2.2 \pm 0.1 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$  (Fig. SI10†). In contrast, excitation of  $[Ru(bpy)_3]^{2+}$  in ascorbate buffer resulted in the immediate formation of reduced PS, with  $k_q = 2.7 \pm 0.3 \times 10^7 \text{ M}^{-1} \text{ s}^{-1}$  (Fig. SI11 and SI12†), consistent with our results on ascorbate diffusion (see Section Surfactant dependency) and results from literature.<sup>48,63–65</sup> According to previous kinetic studies with other PSs and cobalt based WRCs, a fast electron transfer from reduced PS to WRC ( $PS^- \rightarrow \mathbf{1}$ ) was expected.<sup>56,66–68</sup> The electron transfer rate of photogenerated  $PS^-$  to **1** is indeed close to diffusion control with  $k_{ET} = 1.6 \pm 0.1 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$  (Fig. SI13 and SI14†). This rate coincides well with values reported previously for other poly-pyridyl based Co WRCs by Chang or Scandola and co-workers.<sup>64,65</sup> We tentatively propose a similar mechanism for the immobilized systems: excitation of  $5 \rightarrow 5^*$ , followed by reductive quenching by  $H_{asc}^-$  from bulk solution and electron transfer to **3**. The model rationalizes also the increased catalytic performance of cationic (**7**) over anionic surfactants (**6**). According to our detailed and recent study with a similar tetra-pyridyl based Co WRC, we propose the final formation of  $H_2$  to occur by protonation of  $Co^{III}-H$  →  $Co^{III}-H$  →  $Co^{II}-H$  and subsequent protonation and  $H_2$  release.<sup>69</sup>

## Conclusion

A convenient method to immobilize molecular PSs and WRCs on hydrophobic supports by non-covalent interactions is

presented. This photocatalytic architecture can be applied to various molecular PSs and WRCs since derivatizations with long alkyl chains are synthetically versatile, and no active functionalities are present, potentially interfering with the basic catalyst framework. The approach allows moving from homogeneous to heterogeneous catalysis, while mechanistic insights can still be obtained from studies in solution. We exemplify this concept with WRC **3** and PS **5**. No leaching was observed, in agreement with strong hydrophobic interactions. At low concentrations, catalytic activity was still observed while the homogenous systems ceased to produce  $H_2$ . At high concentrations, the homogenous system exceeds the immobilised one in terms of rate, but stability is retained. A proper choice of surfactants improved performance without altering the basic catalytic system. A careful analysis of the concentration dependency showed that immobilized catalysts remained mobile on their supports, and that PS stability limits turnover of catalysis, in line with results from recycling experiments. In summary, highly active molecular catalysts were immobilized by a straightforward and flexible method on cheap and robust supports, which is an important step towards heterogenization and thus physical separation of HER and potentially OER in a molecular water splitting architecture.

## Experimental

### Syntheses

Poly-pyridine ligand **2** (appy),  $[Ru(bpy)_2Cl_2]$  and  $[Ru(bpy)_3]Cl_2$  were prepared according to reported procedures.<sup>54,70,71</sup>

$[Co(C_{18}H_{37}-appy)(H_2O)][ClO_4]_2$  (**3**). Ligand **2** (appy, 200 mg, 0.48 mmol, 1 eq.) and NaH (60% in mineral oil; 55.1 mg, 1.44 mmol, 3 eq.) were stirred in dry DMF (20 mL) for 45 min at rt. Iodo-octadecane (913 mg, 2.4 mmol, 5 eq.) was added and stirring continued for 15 h at rt.  $CH_2Cl_2$  and aq. NaOH (ca. 2 M) were added and the phases separated. The aqueous phase was washed three times with  $CH_2Cl_2$ , the combined organic phases dried over  $MgSO_4$ , filtered and concentrated. The resulting yellowish oil was dissolved in  $MeOH/Et_2O$  (3 : 1, 20 mL) and  $Co(ClO_4)_2$  hexahydrate (175.6 mg, 0.48 mmol, 1 eq.) added. The resulting brown solution was stirred for 3 h at rt followed by precipitation with excess  $Et_2O$ . The solid was filtered off, washed 3× with  $Et_2O$  and dried *in vacuo* to give **3** as light brown solid (358 mg, 0.38 mmol, 79%). ESI-MS (MeOH):  $m/z = 364$  [ $M - 2 ClO_4$ ] $^{2+}$  (100%), [ $M - ClO_4$ ] $^+$  (50%), elemental analysis: calcd. for  $[Co(C_{18}H_{37}-appy)(H_2O)][ClO_4]_2$  (%): C, 55.88; H, 6.07; N, 7.40. Found: C, 56.05; H, 5.98; N, 7.29; UV/vis absorption (MeOH):  $\lambda_{max} = 248 \text{ nm}$  ( $\epsilon = 1800 \text{ M}^{-1} \text{ cm}^{-1}$ ); 299 nm ( $\epsilon = 2400 \text{ M}^{-1} \text{ cm}^{-1}$ ); 455 nm (shoulder,  $\epsilon = 60 \text{ M}^{-1} \text{ cm}^{-1}$ ).

**4-Methyl-4'-nonadecyl-2,2'-bipyridine** (**4**). 4,4'-Dimethyl-2,2'-bipyridyl (0.1 g, 0.54 mmol, 1 eq.) was suspended in dry THF (3 mL) and cooled to  $-45^\circ\text{C}$  in an  $MeOH/dry$  ice bath. LDA (2 M in THF, 0.54 mL, 1.1 mmol, 2 eq.) was slowly added over 30 minutes and the mixture stirred for 2 h at  $-45^\circ\text{C}$ . Afterwards, a solution of 1-bromo-octadecane (271 mg, 0.65 mmol, 1.2 eq.) in dry THF (1 mL) was added drop wise to the reddish/brown solution, and the reaction mixture allowed to warm up to room temperature and further stirred for 15 h. The reaction

mixture was quenched with MeOH (3 mL) and stirred for another 30 min at room temperature followed by concentration. The crude product was purified by flash chromatography (silica gel, EtOAc) to give **4** as colourless solid (209 mg, 0.48 mmol, 88%). <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>, ppm):  $\delta$  = 8.55 (dd, *J* = 5.1 and 3.0 Hz, 2H), 8.23 (unresolved d, 2H), 7.14 (dd, *J* = 5.1 and 1.5 Hz, 2H), 2.70 (t, *J* = 8.1 Hz, 2H), 2.45 (s, 3H), 1.72–1.64 (m, 2H), 1.26 (br s, 32H), 0.89 (unresolved t, 3H). <sup>13</sup>C[<sup>1</sup>H] NMR (75 MHz, CDCl<sub>3</sub>, ppm):  $\delta$  = 152.9, 148.9, 148.1, 128.4, 127.0, 125.6, 124.6, 123.9, 122.0, 121.3, 43.8, 35.8, 35.6, 31.9, 31.1, 30.5, 29.7, 29.54, 29.49, 29.44, 29.38, 29.2, 23.9, 22.7, 21.2, 14.1. ESI-MS (MeOH): *m/z* = 437.7 [M + H]<sup>+</sup> (100%). Elemental analysis: calcd for C<sub>30</sub>H<sub>48</sub>N<sub>2</sub> (%): C, 82.51; H, 11.08; N, 6.41. Found: C, 82.55; H, 11.04; N, 6.38.

**[Ru(bpy)<sub>2</sub>(**4**)](PF<sub>6</sub>)<sub>2</sub> (5).** [Ru(bpy)<sub>2</sub>Cl<sub>2</sub>]<sup>+</sup>·2H<sub>2</sub>O (300 mg, 0.62 mmol, 1 eq.) and **4** (543 mg, 1.24 mmol, 2 eq.) were suspended in H<sub>2</sub>O/EtOH (1 : 1, 130 mL) and heated up to 100 °C for 24 h. The hot reaction mixture was filtered through celite, cooled down to rt and concentrated. The residual solid was washed 3× with 10 mL of hexane and dissolved in water. A threefold excess of NH<sub>4</sub>PF<sub>6</sub> as concentrated aqueous solution was added dropwise to precipitate the complex as PF<sub>6</sub>–salt. Filtration and washing with water followed by drying gave **5** as red solid (498 mg, 0.44 mmol, 71%). UV/vis absorption (H<sub>2</sub>O):  $\lambda_{\text{max}} = 453$  nm ( $\epsilon = 13\,300\,M^{-1}\,cm^{-1}$ ). Luminescence (H<sub>2</sub>O):  $\lambda_{\text{em}} = 623$  nm ( $\Phi_{\text{P,abs}} = 0.07$ ;  $\tau = 789$  ns). <sup>1</sup>H-NMR (300 MHz, CDCl<sub>3</sub>, ppm)  $\delta$  = 9.04–8.99 (m, 4H), 8.56 (s, 1H), 8.49 (s, 1H), 8.17–8.10 (m, 4H), 7.81–7.73 (m, overlapping signals, 4H), 7.63–7.48 (m, overlapping signals, 6H), 7.36–7.29 (m, overlapping signals, 2H), 2.86 (t, *J* = 7.8 Hz, 2H), 2.64 (s, 3H), 1.73 (unresolved quint., 2H), 1.26 (br s, 32H), 0.88 (t, *J* = 6.6 Hz, 3H). ESI-MS (MeOH): *m/z* = 425.4 [M]<sup>2+</sup> (100%), elemental analysis: calcd for C<sub>50</sub>–H<sub>64</sub>N<sub>6</sub>P<sub>2</sub>F<sub>6</sub>Ru (%): C, 52.67; H, 5.66; N, 7.37. Found: C, 52.42; H, 5.60; N, 7.31.

**[C<sub>16</sub>-NMe<sub>3</sub>][OAc] (7).** 0.1 M aqueous stock solution of **7** was obtained by stirring *N,N,N*-trimethylhexadecyl ammonium hydroxide ([C<sub>16</sub>-NMe<sub>3</sub>][OH]; 25% in MeOH, 1.470 mL, 1 mmol) and acetic acid (58  $\mu$ L, 1 mmol) in 7 mL water for 10 min at rt. The MeOH was evaporated and the solution diluted with water up to 10 mL.

## Preparation of different supports

**Spherical porous silica.** Commercially available hydrophobic silica (45–70  $\mu$ m, 480 m<sup>2</sup> g<sup>-1</sup>) was directly used without further modification.

**Spherical non-porous silica.** Porous spherical silica (20 g, *d* = 10  $\mu$ m, 340 m<sup>2</sup> g<sup>-1</sup>) was glowed in an Alox crucible at 1100 °C for 12 h. The resulting solid was suspended in 10% aqueous HNO<sub>3</sub> (110 mL) and refluxed for 5 h followed by filtration and washing with water until the wash solution had pH > 5. Surface measurement by N<sub>2</sub> adsorption (BET) gave a surface of 0.459 m<sup>2</sup> g<sup>-1</sup>. The product was dried *in vacuo* for 5 h and then stirred overnight (15 h) in a solution of trichlorooctadecylsilane (5 mL) in DCM (50 mL). The slurry was filtered, the resulting solid washed with DCM and MeOH and finally concentrated and

dried *in vacuo*. FM measurements of loaded particles showed a particle size of ~7–9  $\mu$ m (Scheme SI5†).

**Fumed silica.** Hydrophilic fumed silica (6 g, 200–300 nm, 200 m<sup>2</sup> g<sup>-1</sup>) was stirred overnight (15 h) in a solution of trichlorooctadecylsilane (4 mL) in DCM (180 mL). The suspension was centrifuged, the particles washed with DCM and MeOH, concentrated and dried *in vacuo*.

## Adsorption of catalysts

Standard procedure to load catalysts on hydrophobic silica: Hydrophobic fumed silica (200 m<sup>2</sup> g<sup>-1</sup>; 447 mg = 89.4 m<sup>2</sup> BET surface area) and the corresponding amounts of WRC 3 and PS 5 (totally 13  $\mu$ mol, added from freshly prepared methanolic stock solutions, giving a loading of 0.15  $\mu$ mol per m<sup>2</sup> silica surface) were suspended in MeOH (15 mL) and stirred for 30 min. Then 0.1 M aqueous surfactant solution (300  $\mu$ L **6** or **7**) was added and the mixture stirred for an additional 10 min followed by addition of aqueous electrolyte solution (0.1 M NaOTf, 15 mL). The mixture was warmed up to 50 °C in a water bath and the MeOH evaporated with a N<sub>2</sub> flow. The resulting aqueous suspension was sonicated for 5 min and centrifuged. The solution was decanted and analyzed by HPLC to ensure full adsorption of catalysts (filtration through 0.22  $\mu$ m syringe filter prior to measurement). The resulting solid was dried at 50 °C with a N<sub>2</sub> flow to give an orange powder.

## Catalysis

Standard preparation of catalysis suspensions/solutions: In a graduated cylinder sodium ascorbate (990.5 mg, 5 mmol) and ascorbic acid (880.5 mg, 5 mmol) were dissolved in water and diluted to 9 mL.

**Heterogeneous catalysis.** Weighted amounts of silica particles with adsorbed PS 5 and WRC 3 were placed in the reaction vessel and the ascorbate buffer solution added. Then the corresponding amount of surfactant was added (**6** or **7**, as 0.1 M aqueous solution) and the particles properly suspended by stirring and sonication. Finally NaOTf (171 mg, 1 mmol) was added as solid and the suspension diluted up to 10 mL. The resulting reaction mixture was analyzed by HPLC (filtered through 0.22  $\mu$ m syringe filter) to exclude leaching of catalysts.

**Homogeneous catalysis.** The ascorbate buffer solution was transferred into the reaction vessel and corresponding amount of [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> and WRC 1 added. Finally NaOTf (171 mg, 1 mmol) was added as solid and the solution diluted up to 10 mL.

The reaction mixtures were connected to an automated sampling system linked to a GC-TCD, degassed with Ar followed by illumination with 453 nm LED ( $85 \pm 2$  mW; photon flux:  $3 \times 10^{-7}$  mol s<sup>-1</sup>). H<sub>2</sub> evolution was measured as described in a previous publication.<sup>52</sup>

## Acknowledgements

The work has been supported by the University Research Priority Program (URPP) LightChEC. We gratefully acknowledge Prof. C. Copèret and Dr T.-C. Ong from the ETH Zurich for the valuable discussions concerning the characterization of the



silica particles. Further we thank A. Kaech, G. Barmettler and C. Aemisegger from the Centre for Microscopy and Image Analysis (University of Zurich) for their support throughout the TEM and FM measurements.

## Notes and references

- 1 S. Styring, *Faraday Discuss.*, 2012, **155**, 357–376.
- 2 Y. Tachibana, L. Vayssières and J. R. Durrant, *Nat. Photonics*, 2012, **6**, 511–518.
- 3 S. Dasgupta, B. S. Brunschwig, J. R. Winkler and H. B. Gray, *Chem. Soc. Rev.*, 2013, **42**, 2213–2214.
- 4 A. J. Cowan and J. R. Durrant, *Chem. Soc. Rev.*, 2013, **42**, 2281–2293.
- 5 J. Luo, J. H. Im, M. T. Mayer, M. Schreier, M. Khaja Nazeeruddin, N.-G. Park, S. D. Tilley, H. Jin Fan and M. Grätzel, *Science*, 2014, **345**, 1593–1596.
- 6 M. G. Walter, E. L. Warren, J. R. McKone, S. W. Boettcher, Q. Mi, E. A. Santori and N. S. Lewis, *Chem. Rev.*, 2010, **110**, 6446–6473.
- 7 T. S. Teets and D. G. Nocera, *Chem. Commun.*, 2011, **47**, 9268–9274.
- 8 S. Berardi, S. Drouet, L. Francas, C. Gimbert-Surin, M. Guttentag, C. Richmond, T. Stolla and A. Llobet, *Chem. Soc. Rev.*, 2014, **43**, 7501–7519.
- 9 M. D. Karkas, O. Verho, E. V. Johnston and B. Akermark, *Chem. Rev.*, 2014, **114**, 11863–12001.
- 10 Z. Han and R. Eisenberg, *Acc. Chem. Res.*, 2014, **47**, 2537–2544.
- 11 B. Limburg, E. Bouwman and S. Bonnet, *Coord. Chem. Rev.*, 2012, **256**, 1451–1467.
- 12 A. Sartorel, M. Bonchio, S. Campagna and F. Scandola, *Chem. Soc. Rev.*, 2013, **42**, 2262–2280.
- 13 V. Artero and M. Fontecave, *Chem. Soc. Rev.*, 2013, **42**, 2338–2356.
- 14 N. Queyriaux, R. T. Jane, J. Massin, V. Artero and M. Chavarot-Kerlidou, *Coord. Chem. Rev.*, 2015, **304–305**, 3–19.
- 15 J. D. Blakemore, R. H. Crabtree and G. W. Brudvig, *Chem. Rev.*, 2015, DOI: 10.1021/acs.chemrev.5b00122.
- 16 F. F. Abdi, L. Han, A. H. Smets, M. Zeman, B. Dam and R. van de Krol, *Nat. Commun.*, 2013, **4**, 2195.
- 17 S. Y. Reece, J. A. Hamel, K. Sung, T. D. Jarvi, A. J. Esswein, J. J. H. Pijpers and D. G. Nocera, *Science*, 2011, **334**, 645–648.
- 18 B. A. Pinaud, J. D. Benck, L. C. Seitz, A. J. Forman, Z. Chen, T. G. Deutsch, B. D. James, K. N. Baum, G. N. Baum, S. Ardo, H. Wang, E. Miller and T. F. Jaramillo, *Energy Environ. Sci.*, 2013, **6**, 1983.
- 19 M. Heitbaum, F. Glorius and I. Escher, *Angew. Chem.*, 2006, **45**, 4732–4762.
- 20 A. F. Trindade, P. M. P. Gois and C. A. M. Afonso, *Chem. Rev.*, 2009, **109**, 418–514.
- 21 D. C. Bailey and S. H. Langer, *Chem. Rev.*, 1981, **81**, 109–148.
- 22 A. Kirschning, *Topics in current Chemistry*, Springer, Germany, 2004.
- 23 L. Zhang, S. Luo and J.-P. Cheng, *Catal. Sci. Technol.*, 2011, **1**, 507–516.
- 24 J. M. Fraile, J. I. Garcia and J. A. Mayoral, *Chem. Rev.*, 2009, **109**, 360–417.
- 25 R. van de Coevering, R. J. M. Klein Gebbink and G. van Koten, *Prog. Polym. Sci.*, 2005, **30**, 474–490.
- 26 D. J. Lockwood, *Nanostructure Science and Technology*, Springer, New York, 2005.
- 27 J. Huang, K. L. Mulfort, P. Du and L. X. Chen, *J. Am. Chem. Soc.*, 2012, **134**, 16472–16475.
- 28 F. Lakadamyali and E. Reisner, *Chem. Commun.*, 2011, **47**, 1695–1697.
- 29 F. Li, B. Zhang, X. Li, Y. Jiang, L. Chen, Y. Li and L. Sun, *Angew. Chem.*, 2011, **50**, 12276–12279.
- 30 F. M. Toma, A. Sartorel, M. Iurlo, M. Carraro, P. Parisse, C. Maccato, S. Rapino, B. R. Gonzalez, H. Amenitsch, T. Da Ros, L. Casalis, A. Goldoni, M. Marcaccio, G. Scorrano, G. Scoles, F. Paolucci, M. Prato and M. Bonchio, *Nat. Chem.*, 2010, **2**, 826–831.
- 31 J. J. Concepcion, J. W. Jurss, P. G. Hoertz and T. J. Meyer, *Angew. Chem.*, 2009, **48**, 9473–9476.
- 32 N. M. Muresan, J. Willkomm, D. Mersch, Y. Vaynzof and E. Reisner, *Angew. Chem.*, 2012, **51**, 12749–12753.
- 33 M. Braumüller, M. Schulz, D. Sorsche, M. Pfeffer, M. Schaub, J. Popp, B. W. Park, A. Hagfeldt, B. Dietzek and S. Rau, *Dalton Trans.*, 2015, **44**, 5577–5586.
- 34 Z. Yu, F. Lia and L. Sun, *Energy Environ. Sci.*, 2015, **8**, 760–775.
- 35 K. Han, M. Wang, S. Zhang, S. Wu, Y. Yanga and L. Sun, *Chem. Commun.*, 2015, **51**, 7008–7011.
- 36 B. C. Martindale, G. A. Hutton, C. A. Caputo and E. Reisner, *J. Am. Chem. Soc.*, 2015, **137**, 6018–6025.
- 37 M. Wang, K. Han, S. Zhang and L. Sun, *Coord. Chem. Rev.*, 2015, **287**, 1–14.
- 38 A. K. Vannucci, L. Alibabaei, M. D. Losego, J. J. Concepcion, B. Kalanyan, G. N. Parsons and T. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 20918–20922.
- 39 F. Li, K. Fan, B. Xu, E. Gabrielsson, Q. Daniel, L. Li and L. Sun, *J. Am. Chem. Soc.*, 2015, **137**, 9153–9159.
- 40 J. D. Blakemore, A. Gupta, J. J. Warren, B. S. Brunschwig and H. B. Gray, *J. Am. Chem. Soc.*, 2013, **135**, 18288–18291.
- 41 M. A. Gross, A. Reynal, J. R. Durrant and E. Reisner, *J. Am. Chem. Soc.*, 2014, **136**, 356–366.
- 42 J. Willkomm, N. M. Muresan and E. Reisner, *Chem. Sci.*, 2015, **6**, 2727.
- 43 D. L. Ashford, B. D. Sherman, R. A. Binstead, J. L. Templeton and T. J. Meyer, *Angew. Chem.*, 2015, **54**, 4778–4781.
- 44 M. Hansen, F. Li, L. Sun and B. König, *Chem. Sci.*, 2014, **5**, 2683–2687.
- 45 S. Troppmann and B. König, *Chem.-Eur. J.*, 2014, **20**, 14570–14574.
- 46 E. E. Meyer, K. J. Rosenberg and J. Israelachvili, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 15739–15746.
- 47 J. M. Guisan, *Immobilization of Enzymes and Cells*, Springer, Germany, 2013.
- 48 M. Nippe, R. S. Khnayzer, J. A. Panetier, D. Z. Zee, B. S. Olaiya, M. Head-Gordon, C. J. Chang, F. N. Castellano and J. R. Long, *Chem. Sci.*, 2013, **4**, 3934.



49 Y. J. Sun, J. P. Bigi, N. A. Piro, M. L. Tang, J. R. Long and C. J. Chang, *J. Am. Chem. Soc.*, 2011, **133**, 9212–9215.

50 W. M. Singh, T. Baine, S. Kudo, S. Tian, X. A. N. Ma, H. Zhou, N. J. deYonker, T. C. Pham, J. C. Bollinger, D. L. Baker, B. Yan, C. E. Webster and X. Zhao, *Angew. Chem., Int. Ed.*, 2012, **51**, 5941–5944.

51 L. Tong, R. Zong and R. P. Thummel, *J. Am. Chem. Soc.*, 2014, **136**, 4881–4884.

52 C. Bachmann, B. Probst, M. Guttentag and R. Alberto, *Chem. Commun.*, 2014, 50.

53 M. Guttentag, A. Rodenberg, C. Bachmann, A. Senn, P. Hamm and R. Alberto, *Dalton Trans.*, 2013, **42**, 334–337.

54 C. Bachmann, M. Guttentag, B. Spingler and R. Alberto, *Inorg. Chem.*, 2013, **52**, 6055–6061.

55 C.-F. Leung, S.-M. Ng, C.-C. Ko, W.-L. Man, J. Wu, L. Chen and T.-C. Lau, *Energy Environ. Sci.*, 2012, **5**, 7903.

56 B. Probst, A. Rodenberg, M. Guttentag, P. Hamm and R. Alberto, *Inorg. Chem.*, 2010, **49**, 6453–6460.

57 L. M. Grant, F. Tiberg and W. A. Ducker, *J. Phys. Chem. B*, 1998, **102**, 4288–4294.

58 J. Jiang, G. Oberdörster and P. Biswas, *J. Nanopart. Res.*, 2008, **11**, 77–89.

59 R. A. French, A. R. Jacobson, B. Kim, A. L. Isley, R. L. Penn and P. C. Baveye, *Environ. Sci. Technol.*, 2009, **43**, 1354–1359.

60 V. S. Sousa and M. R. Teixeira, *Environ. Chem.*, 2013, **10**, 313–322.

61 C. V. Krishnan, C. Creutz, D. Mahajan, H. A. Schwarz and N. Sutin, *Isr. J. Chem.*, 1982, **22**, 98–106.

62 C.-T. Lin, W. Bottcher, M. Chou, C. Creutz and N. Sutin, *J. Am. Chem. Soc.*, 1976, **98**, 6536–6544.

63 G. M. Brown, B. S. Brunschwig, C. Creutz, J. F. Endicott and N. Sutin, *J. Am. Chem. Soc.*, 1979, **101**, 1298–1300.

64 E. Deponti, A. Luisa, M. Natali, E. Iengo and F. Scandola, *Dalton Trans.*, 2014, **43**, 16345–16353.

65 R. S. Khnayzer, V. S. Thoi, M. Nippe, A. E. King, J. W. Jurss, K. A. El Roz, J. R. Long, C. J. Chang and F. N. Castellano, *Energy Environ. Sci.*, 2014, **7**, 1477.

66 B. Probst, M. Guttentag, A. Rodenberg, P. Hamm and R. Alberto, *Inorg. Chem.*, 2011, **50**, 3404–3412.

67 M. Guttentag, A. Rodenberg, R. Kopeleent, B. Probst, C. Buchwalder, M. Brandstätter, P. Hamm and R. Alberto, *Eur. J. Inorg. Chem.*, 2012, 59–64.

68 C. V. Krishnan and N. Sutin, *J. Am. Chem. Soc.*, 1981, **103**, 2141–2142.

69 A. Rodenberg, M. Orazielli, B. Probst, C. Bachmann, R. Alberto, K. K. Baldridge and P. Hamm, *Inorg. Chem.*, 2015, **54**, 646–657.

70 B. P. Sullivan, D. J. Salmon and T. J. Meyer, *Inorg. Chem.*, 1978, **17**, 3334–3341.

71 N. Singh and L. B. Prasad, *Synth. React. Inorg. Met.-Org. Chem.*, 1996, **26**, 627–646.

