


This paper is published as part of a *Nanoscale* themed issue on [doped nanostructures](#)

Guest Editor: Stephen Pearton

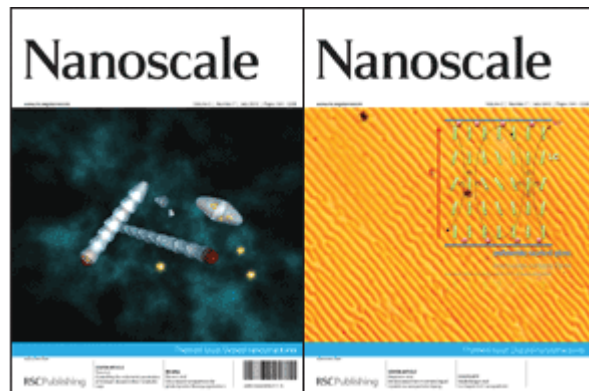

Editorial

[Doped nanostructures](#)

Stephen Pearton, *Nanoscale*, 2010

DOI: [10.1039/c005273f](#)

Review Articles

[Impacts of doping on thermal and thermoelectric properties of nanomaterials](#)

Gang Zhang and Baowen Li, *Nanoscale*, 2010

DOI: [10.1039/c0nr00095g](#)

[Effect of N/B doping on the electronic and field emission properties for carbon nanotubes, carbon nanocones, and graphene nanoribbons](#)

Shan-Sheng Yu and Wei-Tao Zheng, *Nanoscale*, 2010

DOI: [10.1039/c0nr00002g](#)

[Silica-based nanoparticles for photodynamic therapy applications](#)

Pierre Couleaud, Vincent Morosini, Céline Frochot, Sébastien Richeter, Laurence Raehm and Jean-Olivier Durand, *Nanoscale*, 2010

DOI: [10.1039/c0nr00096e](#)

Mini Review

[Co-Doped ZnO nanoparticles: Minireview](#)

Igor Djerdj, Zvonko Jagličić, Denis Aržon and Markus Niederberger, *Nanoscale*, 2010

DOI: [10.1039/c0nr00148a](#)

Communications

[Controlling the volumetric parameters of nitrogen-doped carbon nanotube cups](#)

Brett L. Allen, Matthew B. Keddie and Alexander Star, *Nanoscale*, 2010

DOI: [10.1039/c0nr00043d](#)

[Visible light induced photobleaching of methylene blue over melamine-doped TiO₂ nanocatalyst](#)

Jurate Virkutyte, Babita Baruwati and Rajender S. Varma, *Nanoscale*, 2010

DOI: [10.1039/c0nr00089b](#)

[Selective detection of trace amount of Cu²⁺ using semiconductor nanoparticles in photoelectrochemical analysis](#)

Guang-Li Wang, Jing-Juan Xu and Hong-Yuan Chen, *Nanoscale*, 2010

DOI: [10.1039/c0nr00084a](#)

[Flower-like TiO₂ nanostructures with exposed {001} facets: Facile synthesis and enhanced photocatalysis](#)

Min Liu, Lingyu Piao, Weiming Lu, Siting Ju, Lei Zhao, Chunlan Zhou, Hailing Li and Wenjing Wang, *Nanoscale*, 2010

DOI: [10.1039/c0nr00050g](#)

Papers

[Electroconvection in nematic liquid crystals via nanoparticle doping](#)

Martin Urbanski, Brandy Kinkead, Hao Qi, Torsten Hegmann and Heinz-S. Kitzerow, *Nanoscale*, 2010

DOI: [10.1039/c0nr00139b](#)

[Superhydrophilicity-assisted preparation of transparent and visible light activated N-doped titania film](#)

Qing Chi Xu, Diana V. Wellia, Rose Amal, Dai Wei Liao, Say Chye Joachim Loo and Timothy Thatt Yang Tan, *Nanoscale*, 2010

DOI: [10.1039/c0nr00105h](#)

[The influence of doping on the device characteristics of In_{0.5}Ga_{0.5}As/GaAs/Al_{0.2}Ga_{0.8}As quantum dots-in-a-well infrared photodetectors](#)

G. Jolley, L. Fu, H. H. Tan and C. Jagadish, *Nanoscale*, 2010

DOI: [10.1039/c0nr00128g](#)

[Study of concentration-dependent cobalt ion doping of TiO₂ and TiO_{2-x}N_x at the nanoscale](#)

James L. Gole, Sharka M. Prokes, O. J. Glembocki, Junwei Wang, Xiaofeng Qiu and Clemens Burda, *Nanoscale*, 2010

DOI: [10.1039/c0nr00125b](#)

Multifunctional nanocomposites of superparamagnetic (Fe₃O₄) and NIR-responsive rare earth-doped up-conversion fluorescent (NaYF₄: Yb,Er) nanoparticles and their applications in biolabeling and fluorescent imaging of cancer cells

Congcong Mi, Jingpu Zhang, Huanyu Gao, Xianlong Wu, Meng Wang, Yingfan Wu, Yueqin Di, Zhangrun Xu, Chuanbin Mao and Shukun Xu, *Nanoscale*, 2010
DOI: [10.1039/c0nr00102c](https://doi.org/10.1039/c0nr00102c)

Effect of doping on the morphology and multiferroic properties of BiFeO₃ nanorods

Dimple P. Dutta, O. D. Jayakumar, A. K. Tyagi, K. G. Girija, C. G. S. Pillai and G. Sharma, *Nanoscale*, 2010
DOI: [10.1039/c0nr00100g](https://doi.org/10.1039/c0nr00100g)

Effect of substrate temperature on implantation doping of Co in CdS nanocrystalline thin films

S. Chandramohan, A. Kanjilal, S. N. Sarangi, S. Majumder, R. Sathyamoorthy, C.-H. Hong and T. Som, *Nanoscale*, 2010
DOI: [10.1039/c0nr00123f](https://doi.org/10.1039/c0nr00123f)

Modification of neodymium-doped ZnO hybrid nanoparticles under mild hydrothermal conditions

Behzad Shahmoradi, K. Soga, S. Ananda, R. Somashekar and K. Byrappa, *Nanoscale*, 2010
DOI: [10.1039/c0nr00069h](https://doi.org/10.1039/c0nr00069h)

Ex situ vapor phase boron doping of silicon nanowires using BBr₃

Gregory S. Doerk, Gabriella Lestari, Fang Liu, Carlo Carraro and Roya Maboudian, *Nanoscale*, 2010
DOI: [10.1039/c0nr00127a](https://doi.org/10.1039/c0nr00127a)

Change in conformation of polymer PFO on addition of multiwall carbon nanotubes

Malti Bansal, Ritu Srivastava, C. Lal, M. N. Kamalasanan and L. S. Tanwar, *Nanoscale*, 2010
DOI: [10.1039/c0nr00001a](https://doi.org/10.1039/c0nr00001a)

Amino acid-assisted one-pot assembly of Au, Pt nanoparticles onto one-dimensional ZnO microrods

Xianghong Liu, Jun Zhang, Xianzhi Guo, Shihua Wu and Shurong Wang, *Nanoscale*, 2010
DOI: [10.1039/c0nr00015a](https://doi.org/10.1039/c0nr00015a)

Luminescence resonance energy transfer from an upconverting nanoparticle to a fluorescent phycobiliprotein

Fiorenzo Vetrone, Rafik Naccache, Christopher G. Morgan and John A. Capobianco, *Nanoscale*, 2010
DOI: [10.1039/c0nr00126k](https://doi.org/10.1039/c0nr00126k)

Doping single-walled carbon nanotubes through molecular charge-transfer: a theoretical study

Arun K. Manna and Swapan K. Pati, *Nanoscale*, 2010
DOI: [10.1039/c0nr00124d](https://doi.org/10.1039/c0nr00124d)

Energy transfer study between Ce³⁺ and Tb³⁺ ions in doped and core-shell sodium yttrium fluoride nanocrystals

Pushpal Ghosh, Arik Kar and Amitava Patra, *Nanoscale*, 2010
DOI: [10.1039/c0nr00019a](https://doi.org/10.1039/c0nr00019a)

Pt surface modification of SnO₂ nanorod arrays for CO and H₂ sensors

Hui Huang, C. Y. Ong, J. Guo, T. White, M. S. Tse and O. K. Tan, *Nanoscale*, 2010
DOI: [10.1039/c0nr00159g](https://doi.org/10.1039/c0nr00159g)

Poly (acrylic acid)-capped lanthanide-doped BaFCl nanocrystals: synthesis and optical properties

Qiang Ju, Wenqin Luo, Yongsheng Liu, Haomiao Zhu, Renfu Li and Xueyuan Chen, *Nanoscale*, 2010
DOI: [10.1039/c0nr00116c](https://doi.org/10.1039/c0nr00116c)

Enhanced Cu emission in ZnS: Cu,Cl/ZnS core-shell nanocrystals

Carley Corrado, Morgan Hawker, Grant Livingston, Scott Medling, Frank Bridges and Jin Z. Zhang, *Nanoscale*, 2010
DOI: [10.1039/c0nr00056f](https://doi.org/10.1039/c0nr00056f)

Synthesis and characterization of zirconium-doped mesoporous nano-crystalline TiO₂

Kanattukara Vijayan Bineesh, Dong-Kyu Kim and Dae-Won Park, *Nanoscale*, 2010
DOI: [10.1039/c0nr00108b](https://doi.org/10.1039/c0nr00108b)

Zn-doped nanocrystalline TiO₂ films for CdS quantum dot sensitized solar cells

Guang Zhu, Zujun Cheng, Tian Lv, Likun Pan, Qingfei Zhao and Zhuo Sun, *Nanoscale*, 2010
DOI: [10.1039/c0nr00087f](https://doi.org/10.1039/c0nr00087f)

Effect of synergy on the visible light activity of B, N and Fe co-doped TiO₂ for the degradation of MO

Mingyang Xing, Yongmei Wu, Jinlong Zhang and Feng Chen, *Nanoscale*, 2010
DOI: [10.1039/c0nr00078g](https://doi.org/10.1039/c0nr00078g)

Facile synthesis of lanthanide nanoparticles with paramagnetic, down- and up-conversion properties

Zhengquan Li and Yong Zhang, *Nanoscale*, 2010
DOI: [10.1039/c0nr00073f](https://doi.org/10.1039/c0nr00073f)

Glucose oxidase-doped magnetic silica nanostructures as labels for localized signal amplification of electrochemical immunosensors

Jingjing Ren, Dianping Tang, Biling Su, Juan Tang and Guonan Chen, *Nanoscale*, 2010
DOI: [10.1039/b9nr00416e](https://doi.org/10.1039/b9nr00416e)

The role of ellipticity on the preferential binding site of Ce and La in C₇₈-D_{3h}—A density functional theory study

K. Muthukumar and J. A. Larsson, *Nanoscale*, 2010
DOI: [10.1039/c0nr00021c](https://doi.org/10.1039/c0nr00021c)

Tuning the shape and thermoelectric property of PbTe nanocrystals by bismuth doping

Qian Zhang, Ting Sun, Feng Cao, Ming Li, Minghui Hong, Jikang Yuan, Qingyu Yan, Huey Hoon Hng, Nianqiang Wu and Xiaogang Liu, *Nanoscale*, 2010
DOI: [10.1039/c0nr00115e](https://doi.org/10.1039/c0nr00115e)

Flower-like TiO₂ nanostructures with exposed {001} facets: Facile synthesis and enhanced photocatalysis†

Min Liu,^a Lingyu Piao,^{*b} Weiming Lu,^{ac} Siting Ju,^b Lei Zhao,^a Chunlan Zhou,^a Hailing Li^a and Wenjing Wang^{*a}

Received (in Gainesville, FL, USA) 24th January 2010, Accepted 17th February 2010

First published as an Advance Article on the web 17th March 2010

DOI: 10.1039/c0nr00050g

Flower-like TiO₂ nanostructures with exposed {001} facets were synthesized by a low-temperature hydrothermal process from Ti powders for the first time, and they exhibited enhanced photocatalytic degradation of methylene blue dye under ultraviolet light irradiation.

Titanium oxide (TiO₂), as one of the most important oxides, has been widely investigated due to its numerous applications in photovoltaic cells,¹ photocatalysis,^{2,3} Li-ion battery materials,⁴ sensors⁵ and so on. These applications originate from the unique physical and chemical properties of TiO₂ which depend not only on the crystal phase and particle size but also on the exposed facet.^{6–10} For anatase TiO₂, both theoretical and experimental studies have found that the minority {001} facets in the equilibrium state are especially reactive.^{8–11} However, it has been demonstrated that the average surface energies are $\gamma_{\{001\}} (0.90 \text{ J m}^{-2}) > \gamma_{\{100\}} (0.53 \text{ J m}^{-2}) > \gamma_{\{101\}} (0.44 \text{ J m}^{-2})$.^{7,9,10} Although the higher-surface-energy {001} facets have much higher chemical activities, almost all of anatase TiO₂ micro- and nanostructures reported to date are usually dominated by less-reactive {101} facets, which are thermodynamically stable due to their lower surface energy. Therefore, anatase TiO₂ nanostructures with exposed {001} facets are rarely observed.

An important step forward in the preparation of anatase TiO₂ single crystals with exposed {001} facets were achieved by Lu and co-workers.¹¹ They reported the synthesis of anatase TiO₂ microcrystals with exposed {001} facets by using TiF₄ as the raw material. Since then, several researchers have prepared anatase TiO₂ single crystals with exposed {001} facets from different raw materials, such as titanium tetrafluoride, titanium chloride, tetrabutyl titanate, titanium tetraisopropoxide, and so on.^{12–16} However, these materials have high hydrolytic reaction rates which make it difficult to control their reaction processes. Very recently, anatase TiO₂ sheets with a high percentage of {001} facets were prepared from titanium nitride by Lu and co-workers.¹⁷ However, the price of titanium nitride is still very high. Moreover, all of the previously mentioned experimental

processes require high temperatures,^{11–18} even as high as 1300 °C,¹⁵ which not only increases the production cost but also hinders scaled-up production.

Furthermore, nanomaterials with hierarchical architectures have attracted much attention, since they can possess a number of attractive properties and have a wide range of applications in catalysis, solar cells, Li-ion batteries, and so on.^{19–24} For example, rose-like ZnO nanostructures, which consist of many nanosheets, exhibit enhanced light conversion efficiency in dye-sensitized solar cells (DSSC).²³ Flower-like ZnMn₂O₄ nanostructures, which are composed of numerous nanorods, showed enhanced electrochemical lithium storage.²⁴ However, it remains a great challenge to develop feasible methods for the synthesis of well-defined hierarchical TiO₂ nanostructures.

Herein, we report a simple and facile route for the one-pot synthesis of flower-like TiO₂ nanostructures with exposed {001} facets by a low-temperature hydrothermal process from Ti powders. These flower-like TiO₂ nanostructures with exposed {001} facets have never been reported until now. In agreement with calculations, it can be confirmed that these flower-like TiO₂ nanostructures contain about 10–30% exposed highly reactive {001} facets. Moreover, these flower-like TiO₂ nanostructures exhibited enhanced photocatalytic degradation of methylene blue (MB) dye under ultraviolet (UV) light irradiation, and they also have potential applications in photonic and optoelectronic devices, solar cells, sensors, and so on.

In a typical synthesis, 0.1 g Ti powder (200 mesh, 99.9% purity, see Fig. S1 of the ESI†), 40 ml H₂O and 0.25 ml hydrofluoric acid (40 wt %) were added into a Teflon-lined autoclave. Then, the mixture was kept at 120 °C for 10 h. After completion of the reaction, the products were collected by centrifugation and thoroughly washed with high-purity water (18 M Ω) until pH 7.0 was reached. Finally, the products were dried at 80 °C.

Fig. 1 a and b show typical field-emission scanning electron microscope (FE-SEM) images of the flower-like TiO₂ nanostructures. It can be seen that the TiO₂ product contains numerous flower-like aggregates, and almost all of them show the same morphology. These flower-like TiO₂ nanostructures have a size around 300–700 nm, and they are composed of large numbers of truncated tetragonal pyramidal TiO₂ nanocrystals. The width of their top surface is *ca.* 50–150 nm. The length of the truncated tetragonal pyramidal TiO₂ nanocrystals is *ca.* 100–200 nm. Fig. 1c shows an X-ray diffraction (XRD) pattern of the flower-like TiO₂ nanostructures. All XRD peaks of the synthesized flower-like TiO₂ nanostructures can be indexed to the anatase TiO₂ phase (JCPDS No. 21-1272) and no residual Ti phase can be detected. Remarkably enhanced (101) and

^aKey Laboratory of Solar Thermal Energy and Photovoltaic System, Institute of Electrical Engineering, Chinese Academy of Sciences, No. 6 Beiertiao, Zhongguancun, 100190 Beijing, China. E-mail: wjwangwj@126.com; Fax: (+86) 10-82547041; Tel: (+86) 10-82547042

^bNational Center for Nanoscience and Technology, No.11 Beiyitiao, Zhongguancun, 100190 Beijing, China. E-mail: piaoly@nanoctr.cn; Fax: (+86) 10-82545505; Tel: (+86) 10-82545505

^cInstitute of Metal Research, Chinese Academy of Sciences, Shenyang, 110016, China

† Electronic supplementary information (ESI) available: Additional FE-SEM images. See DOI: 10.1039/c0nr00050g

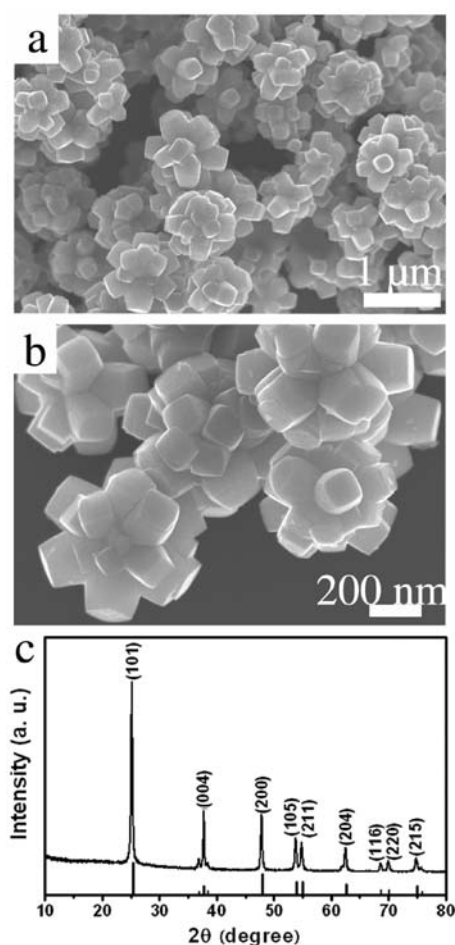


Fig. 1 (a, b) FE-SEM images of the flower-like TiO₂ nanostructures at low and high magnifications, respectively. (c) XRD pattern of the flower-like TiO₂ nanostructures. Vertical bars indicate peak position and intensity of anatase TiO₂ (JCPDS No. 21-1272).

(004) peaks indicate that the TiO₂ nanostructures are dominant in {101} and {001} facets.

Fig. 2a shows a transmission electron microscopy (TEM, FEI F-20) image of the flower-like TiO₂ nanostructures. It confirms that the flower-like TiO₂ nanostructures were composed of many truncated tetragonal pyramidal TiO₂ nanocrystals. An angle of $68.3^\circ \pm 0.3^\circ$, which is consistent with the interfacial angle between {001} and {101},^{11,14,15} was observed on the truncated tetragonal pyramidal TiO₂ nanocrystals. It suggests that the truncated tetragonal pyramidal TiO₂ nanocrystals expose facets of {001} and {101}. Fig. 2b gives a schematic illustration of the flower-like TiO₂ nanostructures. Fig. 2c shows a high-resolution TEM (HRTEM) image of a truncated tetragonal pyramidal TiO₂ nanocrystal with clear crystalline lattice fringes. The lattice spacing of 0.352 nm corresponds to the {101} planes, while the lattice spacing of 0.237 nm corresponds to the {004} planes. The angle labeled in the corresponding fast-Fourier transform (FFT) image (Fig. 2d) is $68.3^\circ \pm 0.3^\circ$, which is identical to the theoretical value for the angle between the {101} and {001} facets. On the basis of the above characterizations, it can be confirmed that the flower-like TiO₂ nanostructures have exposed {001} facets.

It has been demonstrated that metal Ti could react with HF forming TiO₂, under hydrothermal conditions.²⁵ Due to their low

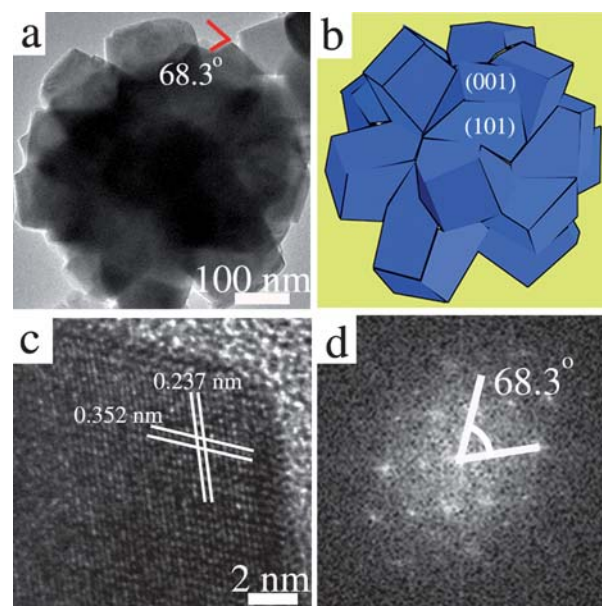


Fig. 2 (a) TEM image of the flower-like TiO₂ nanostructures. (b) Schematic diagram of the flower-like TiO₂ nanostructures. (c) HRTEM image of a truncated tetragonal pyramidal TiO₂ nanocrystal. (d) The corresponding fast-Fourier transform (FFT) pattern.

surface energy, TiO₂ crystals grow with exposed {101} facets mainly during the early stages of synthesis. However, fluorine ions can markedly reduce the surface energy of {001} facets to a level lower than that of {101} facets.¹¹ As a result, {001} facets are exposed during growth, and flower-like TiO₂ nanostructures with exposed {001} facets are formed. Therefore, hydrofluoric acid is believed to have a triple role here: to dissolve the Ti powders, to retard the hydrolysis of the titanium precursor, and to reduce the surface energy.¹⁸

The photocatalytic activity of the flower-like TiO₂ nanostructures was evaluated in terms of the decolorization of MB dye under UV light irradiation. For photocatalytic reaction, the surface fluorine was removed using a heat treatment process at 600 °C in O₂ for 2 h, without altering the morphology (see Fig. S2 of the ESI†). After that, 30 mg flower-like TiO₂ nanostructures was dispersed in 100 ml of aqueous solution containing 0.01 M NaOH and 25 ppm MB.¹² Before exposure to UV light irradiation, the suspension was stirred in the dark for 1 h to allow it reach a complete adsorption–desorption equilibrium. Then the solution was irradiated with $\sim 0.5 \text{ mW cm}^{-2}$ UV light (with a wavelength peak at 365 nm) under continuous stirring. The concentration of MB was determined from the absorbance at the wavelength of 665 nm. For comparison, the same procedure was also done for P25 TiO₂ powders.

As shown in Fig. 3, the flower-like TiO₂ nanostructures exhibited higher activity than that of the commercial P25 TiO₂ powders. The linear relationship of $\ln C/C_0$ vs. time (inset of Fig. 3) shows that the photocatalytic degradation of MB follows pseudo-first-order kinetics, $\ln(C/C_0) = kt$, where C/C_0 is the normalized MB concentration, t is the reaction time, and k is the pseudo-first-rate constant. The apparent photochemical degradation rate constant for the flower-like TiO₂ nanostructures is $1.23 \times 10^{-2} \text{ min}^{-1}$, which is almost two times of that for the P25 TiO₂ powders, $6.73 \times 10^{-3} \text{ min}^{-1}$. This further confirms that the flower-like TiO₂ nanostructures exhibit high photocatalytic efficiency. The enhanced photocatalytic activity of the flower-like TiO₂ nanostructures can be attributed to their

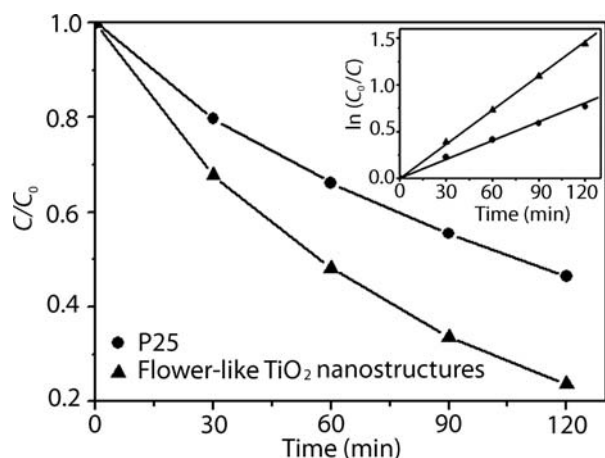


Fig. 3 The variation of MB concentration by photoelectrocatalytic reaction with P25 TiO₂ powders and flower-like TiO₂ nanostructures. The inset shows the pseudo-first-order kinetic rate plots for the photochemical degradation of MB.

three-dimensional (3D) hierarchical nanostructures and exposed {001} facets. 3D hierarchical nanostructures are regarded to have a greater number of active sites than either 1D or 0D architectures.^{26,27} Furthermore, it has been demonstrated that the {001} facets are more reactive toward dissociative adsorption of reactant molecules compared with {101} facets.^{28–32} Therefore, high photocatalytic efficiency is expected for the flower-like TiO₂ nanostructures with {001} facets.

In conclusion, flower-like TiO₂ nanostructures with exposed {001} facets have been successfully synthesized by a low-temperature hydrothermal process from Ti powders for the first time. Owing to their chemically active {001} facets, these TiO₂ nanostructures exhibited enhanced photocatalytic efficiency, and they could possibly be further used in photovoltaic cells, photonic and optoelectronic devices, sensors and so on.

Acknowledgements

This work was supported by the National Natural Science Foundation of China under Grant Nos 60576065 and 50602008, the Knowledge Innovation Program of the Chinese Academy of Sciences under Grant No. KGCXZ-YW-351, and the National High-Techonology Research and Development Programme of China under Grant Nos 2006AA05Z405 and 2007AA05Z437.

References

- 1 B. O'Regan and M. Gratzel, *Nature*, 1991, **353**, 737.
- 2 A. Fujishima and K. Honda, *Nature*, 1972, **238**, 37.
- 3 A. L. Linsebigler, G. Q. Lu and J. T. Yates, *Chem. Rev.*, 1995, **95**, 735.
- 4 V. Subramanian, A. Karki, K. I. Gnanasekar, F. P. Eddy and B. Rambabu, *J. Power Sources*, 2006, **159**, 186.
- 5 N. Wu, S. Wang and I. A. Rusakova, *Science*, 1999, **285**, 1375.
- 6 X. B. Chen and S. S. Mao, *Chem. Rev.*, 2007, **107**, 2891.
- 7 U. Diebold, *Surf. Sci. Rep.*, 2003, **48**, 53.
- 8 X. Gong and A. Selloni, *J. Phys. Chem. B*, 2005, **109**, 19560.
- 9 M. Lazzeri, A. Vittadini and A. Selloni, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2001, **63**, 155409.
- 10 M. Lazzeri, A. Vittadini and A. Selloni, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2002, **65**, 119901.
- 11 H. G. Yang, C. H. Sun, S. Z. Qiao, J. Zou, G. Liu, S. C. Smith, H. M. Cheng and G. Q. Lu, *Nature*, 2008, **453**, 638.
- 12 H. G. Yang, G. Liu, S. Z. Qiao, C. H. Sun, Y. G. Jin, S. C. Smith, J. Zou, H. M. Cheng and G. Q. Lu, *J. Am. Chem. Soc.*, 2009, **131**, 4078.
- 13 X. Han, Q. Kuang, M. Jin, Z. Xie and L. Zheng, *J. Am. Chem. Soc.*, 2009, **131**, 3152.
- 14 Y. Dai, C. M. Cobley, J. Zeng, Y. M. Sun and Y. Xia, *Nano Lett.*, 2009, **9**, 2455.
- 15 F. Amano, O. Prieto-Mahaney, Y. Terada, T. Yasumoto, T. Shibayama and B. Ohtani, *Chem. Mater.*, 2009, **21**, 2601.
- 16 D. Zhang, G. Li, X. Yang and J. C. Yu, *Chem. Commun.*, 2009, 4381.
- 17 G. Liu, H. G. Yang, X. W. Wang, L. Cheng, J. Pan, G. Q. Lu and H. M. Cheng, *J. Am. Chem. Soc.*, 2009, **131**, 12868.
- 18 M. Liu, L. Pao, L. Zhao, S. Ju, Z. Yan, T. He, C. Zhou and W. Wang, *Chem. Commun.*, 2010, **46**, 1664.
- 19 F. Lu, W. Cai and Y. Zhang, *Adv. Funct. Mater.*, 2008, **18**, 1047.
- 20 B. Li, G. Rong, Y. Xie, L. Huang and C. Feng, *Inorg. Chem.*, 2006, **45**, 6404.
- 21 Y. Ma, S. Weiner and L. Addadi, *Adv. Funct. Mater.*, 2007, **17**, 2693.
- 22 Z. Liu, X. Zhang, S. Nishimoto, M. Jin, D. A. Tryk, T. Murakami and A. Fujishima, *Langmuir*, 2007, **23**, 10916.
- 23 E. Hosono, S. Fujihara and T. Kimura, *Electrochim. Acta*, 2004, **49**, 2287.
- 24 L. Xiao, Y. Yang, J. Yin, Q. Li and L. Zhang, *J. Power Sources*, 2009, **194**, 1089.
- 25 G. Wu, J. Wang, D. F. Thomas and A. Chen, *Langmuir*, 2008, **24**, 3503.
- 26 C. Z. Wu, Y. Xie, L. Y. Lei, S. Q. Hu and C. Z. OuYang, *Adv. Mater.*, 2006, **18**, 1727.
- 27 X. L. Hu, J. C. Yu and J. M. Gong, *J. Phys. Chem. C*, 2007, **111**, 11180.
- 28 A. Vittadini, A. Selloni, F. P. Rotzinger and M. Gratzel, *Phys. Rev. Lett.*, 1998, **81**, 2954.
- 29 G. S. Herman, Z. Dohnalek, N. Ruzycski and U. Diebold, *J. Phys. Chem. B*, 2003, **107**, 2788.
- 30 A. Tilocca and A. Selloni, *J. Phys. Chem. B*, 2004, **108**, 19314.
- 31 C. Arrouvel, M. Digne, M. Breyse, H. Toulhoat and P. Raybaud, *J. Catal.*, 2004, **222**, 152.
- 32 A. Selloni, *Nat. Mater.*, 2008, **7**, 613.