

## RESEARCH ARTICLE

View Article Online  
View Journal | View IssueCite this: *Inorg. Chem. Front.*, 2024,  
11, 3607Temperature-dependent self-trapped models  
regulating energy transfer in rare earth double  
perovskites via  $5s^2$  electron doping†Chujun Tan, Shuai Zhang, Haiyan Wang, Jiandong Yao, Hongbang Liu,\*  
Bingsuo Zou \* and Ruosheng Zeng \*

Due to their environmental friendliness, structural plasticity, and tunable emission, lead-free halide double perovskites offer a broad spectrum of applications in light-emitting diode (LED), photodetectors, infrared imaging, and temperature sensing. Herein, we synthesized rare earth-based  $\text{Cs}_2\text{NaYCl}_6$  double perovskites using a solvothermal method, and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doping can effectively modulate the luminescence by adjusting the band gap structure and channels of energy transfer. With the  $\text{Sm}^{3+}$ -feeding concentration increasing, the emission could be adjusted from blue to white, attributed to an effective energy transfer from the self-trapped state to  $\text{Sm}^{3+}$ . Temperature-dependent photoluminescence spectra indicate that the double self-trapped exciton emission at low temperatures originated from two minima in the excited state of  $^3\text{P}_1$ . The relative sensitivity of the optical temperature sensor reached  $1.08\% \text{ K}^{-1}$ , which was better than that of other rare earth perovskites. The LED device based on  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$ @polymethylmethacrylate displays a chromaticity coordinate of (0.29, 0.28), a color rendering index of 87, and the correlated color temperature of 10 986 K. Our work explores an in-depth understanding of energy transfer in double self-trapped states and provides new material for advanced applications.

Received 13th March 2024,  
Accepted 6th May 2024

DOI: 10.1039/d4qi00649f

rsc.li/frontiers-inorganic

## 1. Introduction

Lead-based halide perovskites ( $A = \text{MA}^+/\text{FA}^+/\text{Cs}^+$  and  $X = \text{Cl}^-/\text{Br}^-/\text{I}^-$ ), typically characterized by  $\text{APbX}_3$ , have garnered significant attention due to their excellent photovoltaic properties, including high light absorption coefficients, low defect densities, and large electron sizes.<sup>1–3</sup> Based on these advantages, lead-based perovskites have been found to have broad applications in many fields, such as light emitting diodes (LEDs) and<sup>4,5</sup> X-ray detectors.<sup>6</sup> The disadvantages of a low stability and environmental unfriendliness are also accompanied by lead-based perovskites.<sup>7</sup> However, environmentally friendly cation substitution is an effective strategy to overcome the toxicity of  $\text{Pb}^{2+}$  ions. Replacing two  $\text{Pb}^{2+}$  cations as  $\text{B}^+$  and  $\text{B}^{3+}$  sites in halide double perovskites with the formula  $\text{A}_2\text{B}^+\text{B}^{3+}\text{X}_6$  (e.g.  $\text{Cs}_2\text{NaInCl}_6$ )<sup>8</sup> is a universal strategy.<sup>9–15</sup> However, indirect bandgap or parity prohibited transition cause a weak photoluminescence (PL) in pristine lead-free perovskites. Doping with metal ions or alloying can alter the bandgap or disrupt the symmetry of double perovskites, breaking forbidden tran-

sitions and thereby enhancing their optical properties. By introducing  $\text{Na}^+$  and  $\text{Bi}^{3+}$  into the  $\text{Cs}_2\text{AgInCl}_6$  host, Tang's group broke the inversion-symmetry-induced parity-forbidden transition and reduced the electronic dimensionality of the semiconductor, thus achieving an effective white light emission.<sup>16</sup> By introducing  $\text{Sb}^{3+}$  into the  $\text{Cs}_2\text{NaInCl}_6$  host, our group effectively regulated the density of states (DOS) and significantly enhanced the PL quantum yield (QY) of the self-trapped exciton (STE) (up to 75.89%).<sup>8</sup> However, aforementioned studies only achieved a single luminescence mode. It is widely recognized that doping with rare earth elements is an effective method for tuning luminescent color.<sup>17–22</sup> Rare earth ions typically exhibit a wide emission range from ultraviolet (UV) to infrared due to their rich ( $4f^n$ ) electronic configurations, along with long PL lifetimes and excellent optical stability.<sup>23–26</sup> Xia's group reported on  $\text{Bi}^{3+}:\text{Cs}_2\text{Ag}(\text{In}_{1-x}\text{Tb}_x)\text{Cl}_6$  halide perovskites,<sup>27</sup> which modulated luminescence from green to orange. However, the tuning range of luminescence did not extend to cover the entire spectrum. Tang *et al.* confirmed the existence of an energy transfer from a STE to a rare earth in  $\text{Ho}^{3+}:\text{Cs}_2(\text{Na}, \text{Ag})\text{InCl}_6$  and fabricated white LED.<sup>28</sup> Zhu *et al.* obtained white light emission by combining  $\text{CsPbBr}_3$  NCs and  $\text{Cs}_2\text{Ag}_{1-x}\text{K}_x\text{In}_{0.125}\text{Bi}_{0.875}\text{Cl}_6$  double perovskites.<sup>29</sup> The stability of double perovskites is significantly improved through  $\text{K}^+$  ion alloying. However, the lower PLQY of 15.96% limited broader application. Overall, abovementioned

State Key Laboratory of Featured Metal Materials and Life-cycle Safety for Composite Structures, School of Physical Science and Technology, Guangxi University, Nanning 530004, China. E-mail: liuhb@gxu.edu.cn, zoubs@gxu.edu.cn, zengrsh@guet.edu.cn  
† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4qi00649f>

works only focus on LED applications and do not realize the multi-functional application of phosphors. Furthermore, the luminescence of all these works originates from the single self-trapped state and how to regulate the energy transfer process is not understood in depth.

In this work,  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  were synthesized by a solvent-thermal method, resulting in the emission color transitioning steadily from blue to warm white with increasing  $\text{Sm}^{3+}$  feeding concentration. When a 2%  $\text{Sm}^{3+}$  precursor is the feed, the PLQY is as high as 68%. We propose a model to explain physical processes associated with energy transfer from the STE to the  $\text{Sm}^{3+}$  energy level. The single STE emission was observed at a higher temperature (up to 260 K), but the excited state  $^3\text{P}_1$  was split into two minima and resulted in a double STE emission at a lower temperature (below 260 K).  $5s^2$  electron doping ( $\text{Sb}^{3+}$ -doping) facilitates the energy transfer efficiency. Furthermore, we attempted multi-functional applications of the phosphors. At room temperature, the LED device exhibits chromaticity coordinates (CIE) of (0.28, 0.29), a color rendering index (CRI) of 87 and the correlated color temperature (CCT) of 10 986 K, and the efficient infrared emission (400–1250 nm) is suitable for advanced infrared imaging. Further, the non-contact optical thermometry of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  has demonstrated that absolute and relative sensitivities can reach  $0.14\% \text{ K}^{-1}$  and  $1.08\% \text{ K}^{-1}$ , respectively. Our work provides new physical insights into regulating energy transfer and references for the rational design of functional materials.

## 2. Results and discussion

Pristine and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  are of a highly symmetric three-dimensional cubic structure belonging to the  $Fm\bar{3}m$  space group.  $\text{Cs}_2\text{NaYCl}_6$  consists of alternately arranged  $[\text{NaCl}_6]^{5-}$  and  $[\text{YCl}_6]^{3-}$  octahedra (Fig. 1a). The powder X-ray diffraction (PXRD) analysis reveals that the introduction of  $\text{Sb}^{3+}$  ions causes a shift in diffraction peaks towards higher angles, as seen in Fig. 1b. This shift is due to the smaller ionic radius of  $\text{Sb}^{3+}$  (76.0 pm) compared to that of  $\text{Y}^{3+}$  (90.0 pm), which results in the contraction of the lattice. Conversely, an increase in the  $\text{Sm}^{3+}$ -feeding concentration leads to the diffraction peaks shifting towards lower angles. This shift originates from the substitution of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  ions for  $\text{Y}^{3+}$  ions due to the larger ionic radius of  $\text{Sm}^{3+}$  (95.8 pm) compared to that of  $\text{Y}^{3+}$  (90.0 pm), and lattice expansion dominates a further shift. Due to the low doping content, no large change in lattice parameters was observed. The impurity peaks at  $31.7^\circ$  and  $45.6^\circ$  were from NaCl; however, a slight excess of NaCl is necessary for synthesizing samples with high yields. The X-ray photoelectron spectra (XPS) of pristine and doped perovskites show that the peaks at 160.4 and 158.5 eV are attributed to the Y 3d orbital (Fig. 1c) with no significant deviations. Fig. 1d shows the peaks of the Sb 3d orbital of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$ , which are located at 535.9 and 531.9 eV. Moreover, Fig. 1e shows the peak of the Sb 3d orbital, which is located at

1088.4 eV. The XPS spectra of Cs, Na and Cl of pristine and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  samples in Fig. S1† indicate that no striking deviations in binding energies are observed between pristine and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  perovskites, which is attributed to the strong electronegativity of the rare earth ions. As shown in Fig. 1f, a scanning electron microscopy (SEM) image shows that the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  perovskites are of micrometer scale. Furthermore, the energy-dispersive X-ray spectroscopy (EDS) mapping indicated Cs, Na, Y, Cl, Sb and Sm elements were uniformly distributed in the crystal.

To further investigate the optical properties of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$ , PL, PL excitation (PLE), time-resolved PL (TRPL), and absorption spectroscopy have been performed. As shown in Fig. S2,† the absorption spectrum of pristine  $\text{Cs}_2\text{NaYCl}_6$  shows a strong absorption at 310 nm and two weak absorption bands at 355 and 402 nm. After  $\text{Sb}^{3+}$  doping, the whole absorption band is enhanced, and a new absorption band appears at 260 and 300 nm originating from the  $^1\text{S}_0 \rightarrow ^3\text{P}_1$  of  $\text{Sb}^{3+}$ . The absorption spectra of  $\text{Sm}^{3+}$ -doped samples are basically the same as those of undoped samples, which indicate that the introduction of  $\text{Sm}^{3+}$  does not contribute to the absorption, or absorption peaks overlap. As shown in Fig. S3a,† under 268 nm excitation, the double perovskites exhibit a broadband blue emission centered at 465 nm with a Stokes shift of 1.96 eV. After  $\text{Sb}^{3+}$  doping, the PL intensity of  $\text{Sb}^{3+}:\text{Cs}_2\text{NaYCl}_6$  is more than 10 times that of the pristine sample, with a Stokes shift of 0.93 eV. A large Stokes shift is a distinctive feature of STE emission. Simultaneously, the PL intensity of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  is significantly enhanced by  $\text{Sb}^{3+}$  doping, achieving more than 30 times that of  $\text{Sm}^{3+}:\text{Cs}_2\text{NaYCl}_6$ , as illustrated in Fig. S3b.† As a bridge of energy transfer,  $5s^2$  dopants can more effectively transfer excited electrons from the excited state to the energy level of the rare earth ions. This is because STE emission possesses a wide excitation region and large absorption strength, which can overcome the weak absorption of the f–f transition through the efficient energy transfer. These indicate that the doping of  $\text{Sb}^{3+}$  greatly improves the luminescence efficiency of the samples. At room temperature, under 345 nm excitation, the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites exhibits STE emission centered at 465 nm (Fig. 2a), where the visible (VIS) emission at 565, 603, 651 and 712 nm is from the  $^4\text{G}_{5/2} \rightarrow ^6\text{H}_{J=(5/2, 7/2, 9/2, 11/2)}$  energy level transitions of  $\text{Sm}^{3+}$ , and the near-infrared (NIR) emission at 941, 951, 1026 and 1170 nm is from the  $^4\text{G}_{5/2} \rightarrow ^6\text{F}_{K=(9/2, 7/2, 5/2, 3/2)}$  energy level transitions of  $\text{Sm}^{3+}$ .<sup>30</sup> By normalizing the intensity of STE emission at 465 nm, the intensity of the rare earth emission from  $\text{Sm}^{3+}$  is gradually enhanced with increasing  $\text{Sm}^{3+}$ -feeding concentration. Three excitation peaks at 285, 320, and 345 nm of the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites at different emissions can be observed in Fig. 2b. The peak at 285 nm is attributed to the transition from the singlet  $^1\text{S}_0$  to  $^1\text{P}_1$  of  $\text{Sb}^{3+}$ , while excitation peaks at 320 and 345 nm correspond to the transitions from the ground state  $^1\text{S}_0$  to triplet  $^3\text{P}_1$ . The excitation peak at 410 nm originates from the  $^6\text{H}_{5/2} \rightarrow ^4\text{F}_{7/2}$  tran-





**Fig. 2** (a) Normalized PL spectra of the 1% Sb<sup>3+</sup>, x% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> (x = 1, 2, 3, 4 and 5) double perovskites with different Sm<sup>3+</sup>-feeding concentrations under 345 nm excitation. (b) PLE spectra of the 1% Sb<sup>3+</sup>, 2% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> double perovskites at different emissions. (c) PLE spectra of the 1% Sb<sup>3+</sup>, 2% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> double perovskites under different NIR emissions. (d) Normalized PL spectra of the 1% Sb<sup>3+</sup>, 2% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> double perovskites under different excitations. (e) Integral area ratio S<sub>550–750</sub>/S<sub>400–550</sub> of the STE emission to Sm<sup>3+</sup> emission in 1% Sb<sup>3+</sup>, x% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> (x = 1, 2, 3, 4 and 5) crystals with different Sm<sup>3+</sup>-feeding concentrations. (f) Integral area ratio of S<sub>550–750</sub>/S<sub>400–550</sub> of the 1% Sb<sup>3+</sup>, 2% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> double perovskites under different excitations. (g) PL decay curves of the 1% Sb<sup>3+</sup>, x% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> (x = 1, 2, 3, 4 and 5) double perovskites monitored at 465 nm. (h) PL lifetimes and energy transfer efficiency of the 1% Sb<sup>3+</sup>, x% Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> (x = 1, 2, 3, 4 and 5) double perovskites with different Sm<sup>3+</sup>-feeding concentrations.

Table S1.† The PL lifetime at 465 nm decreases from 1.21 to 0.79 μs with increasing Sm<sup>3+</sup>-feeding concentration. All the emissions exhibit microsecond lifetimes corresponding to the <sup>1</sup>S<sub>0</sub> → <sup>3</sup>P<sub>1</sub> transition of Sb<sup>3+</sup>. This changing trend indicates an efficient energy transfer from the STE to Sm<sup>3+</sup> exists (Fig. 2h). The energy transfer efficiency of the STE to Sm<sup>3+</sup> can be expressed by the following eqn (1):<sup>27,33</sup>


$$\eta = 1 - \frac{\tau_x}{\tau_0}, \quad (1)$$

where τ<sub>0</sub> and τ<sub>x</sub> are the PL lifetimes of STE emission without and with Sm<sup>3+</sup> doping. The energy transfer efficiencies with

different Sm<sup>3+</sup>-feeding concentrations are 2.48% (Sm<sup>3+</sup>:1%), 4.96% (Sm<sup>3+</sup>:2%), 14.05% (Sm<sup>3+</sup>:3%), 21.49% (Sm<sup>3+</sup>:4%), and 34.71% (Sm<sup>3+</sup>:5%). These indicate that the energy transfer efficiency increases with increasing Sm<sup>3+</sup>-feeding concentration. The PL lifetimes of Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> at 651 and 951 nm decreases with Sm<sup>3+</sup>-feeding concentration and are of the millisecond scale (Fig. S6†), suggesting concentration quenching due to the increased Sm<sup>3+</sup>-feeding concentration. A schematic diagram of the photophysical mechanism of the Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> double perovskites at a high temperature is shown in Fig. S7.† The electrons transitioned from the ground state (GS) to the free electron (FE)

state under ultraviolet excitation. Then, through Intersystem Crossing (ISC), the excited electrons arrive at the  $^3P_1$  energy level of  $Sb^{3+}$ , via the  $^3P_1 \rightarrow ^1S_0$  transition producing STE emission and part of the energy transmitted to the excitation level  $^4G_{5/2}$  of  $Sm^{3+}$ , further generating the corresponding  $Sm^{3+}$  emission by radiative recombination.

To gain more understanding about the electron-optical phonon coupling of 1%  $Sb^{3+}$ , 2%  $Sm^{3+}$  co-doped  $Cs_2NaYCl_6$ , temperature-dependent PL spectroscopy was utilized to explore the photophysical process. The PL spectra at 140 and 300 K are shown in Fig. 3a. The PL spectra shows a double STE emission at 140 K and only a single STE emission at 300 K. The emis-

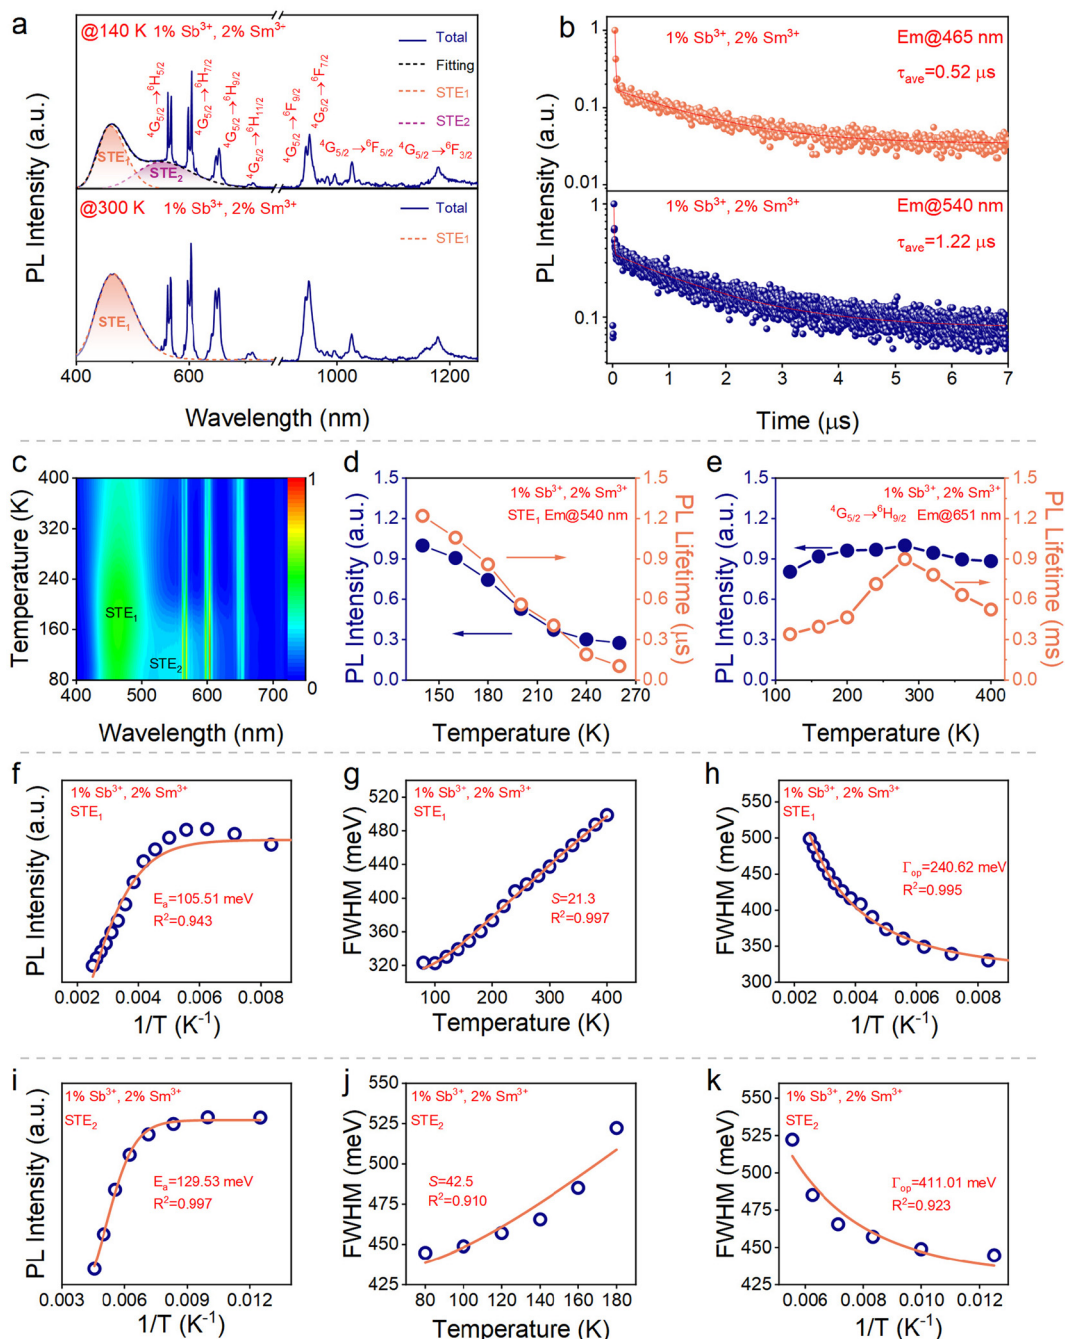

**Fig. 3** (a) PL spectra of 1%  $Sb^{3+}$ , 2%  $Sm^{3+}$  co-doped  $Cs_2NaYCl_6$  at 140 and 300 K. (b) PL lifetime of 1%  $Sb^{3+}$ , 2%  $Sm^{3+}$  co-doped  $Cs_2NaYCl_6$  at 140 and 300 K. (c) Pseudo-color map from temperature-dependent PL spectra of 1%  $Sb^{3+}$ , 2%  $Sm^{3+}$  co-doped  $Cs_2NaYCl_6$ . The evolutions of the PL lifetime and intensity at 540 (d) and 651 nm (e) with temperature. The fitted exciton activation energy  $E_a$  (f), Huang-Rhys factor  $S$  (g) and electron-optical phonon coupling (h) of STE<sub>1</sub>. The fitted exciton activation energy  $E_a$  (i), Huang-Rhys factor  $S$  (j) and electron-optical phonon coupling (k) of STE<sub>2</sub>.

sion centered at 465 nm is defined as STE<sub>1</sub>, and the emission centered at 550 nm is defined as STE<sub>2</sub>. Comparing Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> with similar Sb-doped systems,<sup>34</sup> there are two possible explanations for the double STE emission at low temperatures. One is due to the bimodality that arises from the dynamical Jahn–Teller coupling of the orbital triplet state <sup>3</sup>P<sub>1</sub> to two minima.<sup>35</sup> The excited state shows two minima, which result in two different emission bands. Another reason is that the single state <sup>1</sup>P<sub>1</sub> → <sup>1</sup>S<sub>0</sub> transition and triple state <sup>3</sup>P<sub>1</sub> → <sup>1</sup>S<sub>0</sub> transition co-exist together. To study the source of the double STE emission at low temperatures, the lifetimes of STE<sub>1</sub> and STE<sub>2</sub> emissions were monitored separately at 140 K (Fig. 3b). The PL lifetimes of 0.52 and 1.22 μs for high-energy and low-energy emissions are obtained (Fig. 3b), respectively. The PL lifetimes of both STE emissions are in the microsecond scale. Sb<sup>3+</sup> is characterized by a typical electron configuration of 5s<sup>2</sup>,<sup>36</sup> exhibiting STE emission with nanosecond lifetimes resulting from the transition of <sup>1</sup>P<sub>1</sub> to <sup>1</sup>S<sub>0</sub><sup>37</sup> and microsecond lifetimes arising from the transition of <sup>3</sup>P<sub>1</sub> to <sup>1</sup>S<sub>0</sub>. Therefore, the STE<sub>1</sub> and STE<sub>2</sub> emissions of Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> belong to the triplet state emission. Temperature-dependent PL spectra and pseudo-color maps are shown in Fig. 3c and S8,† and double STE emission can be clearly detected from 80 to 260 K and Sm<sup>3+</sup> emission positions are largely independent of temperature. This is because the f–f transition of rare earths is not easily affected by temperature, and the two minima of the <sup>3</sup>P<sub>1</sub> orbital of Sb<sup>3+</sup> result in a double STE emission at low temperatures. Fig. 3d shows the variation of PL lifetime and intensity at 540 nm from 140 to 260 K, and both show a decreasing trend with increasing temperatures due to thermal quenching. As shown in Fig. S9,† the PL intensity at 465 nm increases gradually with temperature. This is attributed to the electrons gaining more energy and so tend to a higher energy radiative transition with increasing temperature. Fig. 3e shows the variation of PL lifetime and intensity at 651 nm from 120 to 400 K. PL intensity and lifetime increase from 120 to 280 K, which is attributed to the weakening of phonon scattering and reduction of defects more favorable to radiative recombination at low temperature. While PL intensity and lifetime show a decreasing trend from 280 to 400 K, which is attributed to thermal quenching at the high temperature. As shown in Fig. 3f and i, STE<sub>1</sub> and STE<sub>2</sub> were fitted using eqn (2), respectively.<sup>38,39</sup>

$$I(t) = I_0 / (1 + Ae^{-E_a / TK_B}), \quad (2)$$

where  $I(t)$  is the integrated PL intensity at the experimental temperature,  $E_a$  is the exciton activation energy.  $I_0$  is the integrated intensity at 0 K,  $K_B$  is the Boltzmann constant, and  $T$  is the temperature. For STE<sub>1</sub> and STE<sub>2</sub>, exciton activation energies are 105.51 and 129.53 meV, respectively. These values significantly exceed the thermal activation energy of 26 meV at room temperature. This suggests that the highly localized STE are stable.

Huang Rhys factor  $S$  is obtained by fitting the full width at half-maximum (FWHM) and temperature ( $T$ ) using the following eqn (3):<sup>16,40</sup>

$$\text{FWHM}(T) = 2.36\sqrt{S}\hbar\omega_{\text{phonon}}\sqrt{\coth\frac{\hbar\omega_{\text{phonon}}}{2K_B T}}, \quad (3)$$


where  $\hbar\omega_{\text{phonon}}$  is the phonon frequency,  $K_B$  is the Boltzmann constant, and  $T$  is the thermodynamic temperature. The value of  $S$  represents the electron–phonon coupling parameter, directly influencing the degree of lattice distortion and manifesting in a significant Stokes shift.<sup>41,42</sup> STE<sub>2</sub> exhibits a greater Stokes shift than that of STE<sub>1</sub>, as depicted in Fig. S10.†  $S$  values for STE<sub>1</sub> and STE<sub>2</sub> are 21.3 and 42.5, respectively, suggesting that STE<sub>2</sub> experiences a greater lattice distortion (Fig. 3g and j).

The electron–optical phonon coupling energy  $\Gamma_{\text{op}}$  was fitted using the following eqn (4):<sup>43</sup>

$$\Gamma(T) = \Gamma_0 + \Gamma_{\text{op}} / (e^{\hbar\omega_{\text{op}} / K_B T} - 1), \quad (4)$$

where  $\Gamma_0$  represents the intrinsic line width at 0 K, and  $\hbar\omega_{\text{op}}$  denotes the longitudinal optical phonon energy. According to eqn (4), the values of  $\Gamma_{\text{op}}$  for STE<sub>1</sub> and STE<sub>2</sub> are determined as 240.62 and 411.01 meV, respectively (Fig. 3h and k). These  $\Gamma_{\text{op}}$  values indicate a substantial interaction between electrons and phonons, as well as the Jahn–Teller effect contributing to the lattice transient STE<sub>2</sub> having a greater electro-phonon coupling energy, implying stronger Jahn–Teller effect and lattice distortions, which match its larger  $S$  value.<sup>44</sup> Fig. S11† depicts a schematic illustration of the physical mechanism of Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> at low temperatures. This is somewhat different from the mechanism diagram at high temperatures (Fig. S7†). When the excited electrons arrive, the <sup>3</sup>P<sub>1</sub> energy level of Sb<sup>3+</sup> and two minima in the <sup>3</sup>P<sub>1</sub> energy level result in a double STE emission at low temperatures. Meanwhile, benefiting from the energy-transfer channel from STE to Ln<sup>3+</sup>, part of the energy can be transferred to the Sm<sup>3+</sup> ions to emit multicolor.


To get a better knowledge of the electrical structure and luminous characteristics of Cs<sub>2</sub>NaYCl<sub>6</sub> and Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub>, we performed density functional theory (DFT) calculations on pristine and Sb<sup>3+</sup>/Sm<sup>3+</sup> co-doped Cs<sub>2</sub>NaYCl<sub>6</sub> structures. Because of the covalent states of Sb<sup>3+</sup>/Sm<sup>3+</sup> and Y<sup>3+</sup>, a [SbCl<sub>6</sub>]<sup>3-</sup> and [SmCl<sub>6</sub>]<sup>3-</sup> octahedron is used to replace the [YCl<sub>6</sub>]<sup>3-</sup> octahedron. It is found that pristine Cs<sub>2</sub>NaYCl<sub>6</sub> exhibits a flat energy band structure with a direct band gap of 5.01 eV (Fig. 4a). After Sb<sup>3+</sup> doping, the emergence of a new energy level results in a narrower bandgap of 3.75 eV (Fig. 4b). Furthermore, both structures have very flat energy bands with limited dispersion, indicating a large effective mass and confined properties for electrons and holes, which promotes the creation of highly localized electron distributions. The calculated DOS reveals that the valence band maximum (VBM) of Cs<sub>2</sub>NaYCl<sub>6</sub> primarily comprises the Cl 3p state, while the conduction band minimum (CBM) is composed of Y 4d and Cl 3p states, as illustrated in Fig. 4c. The

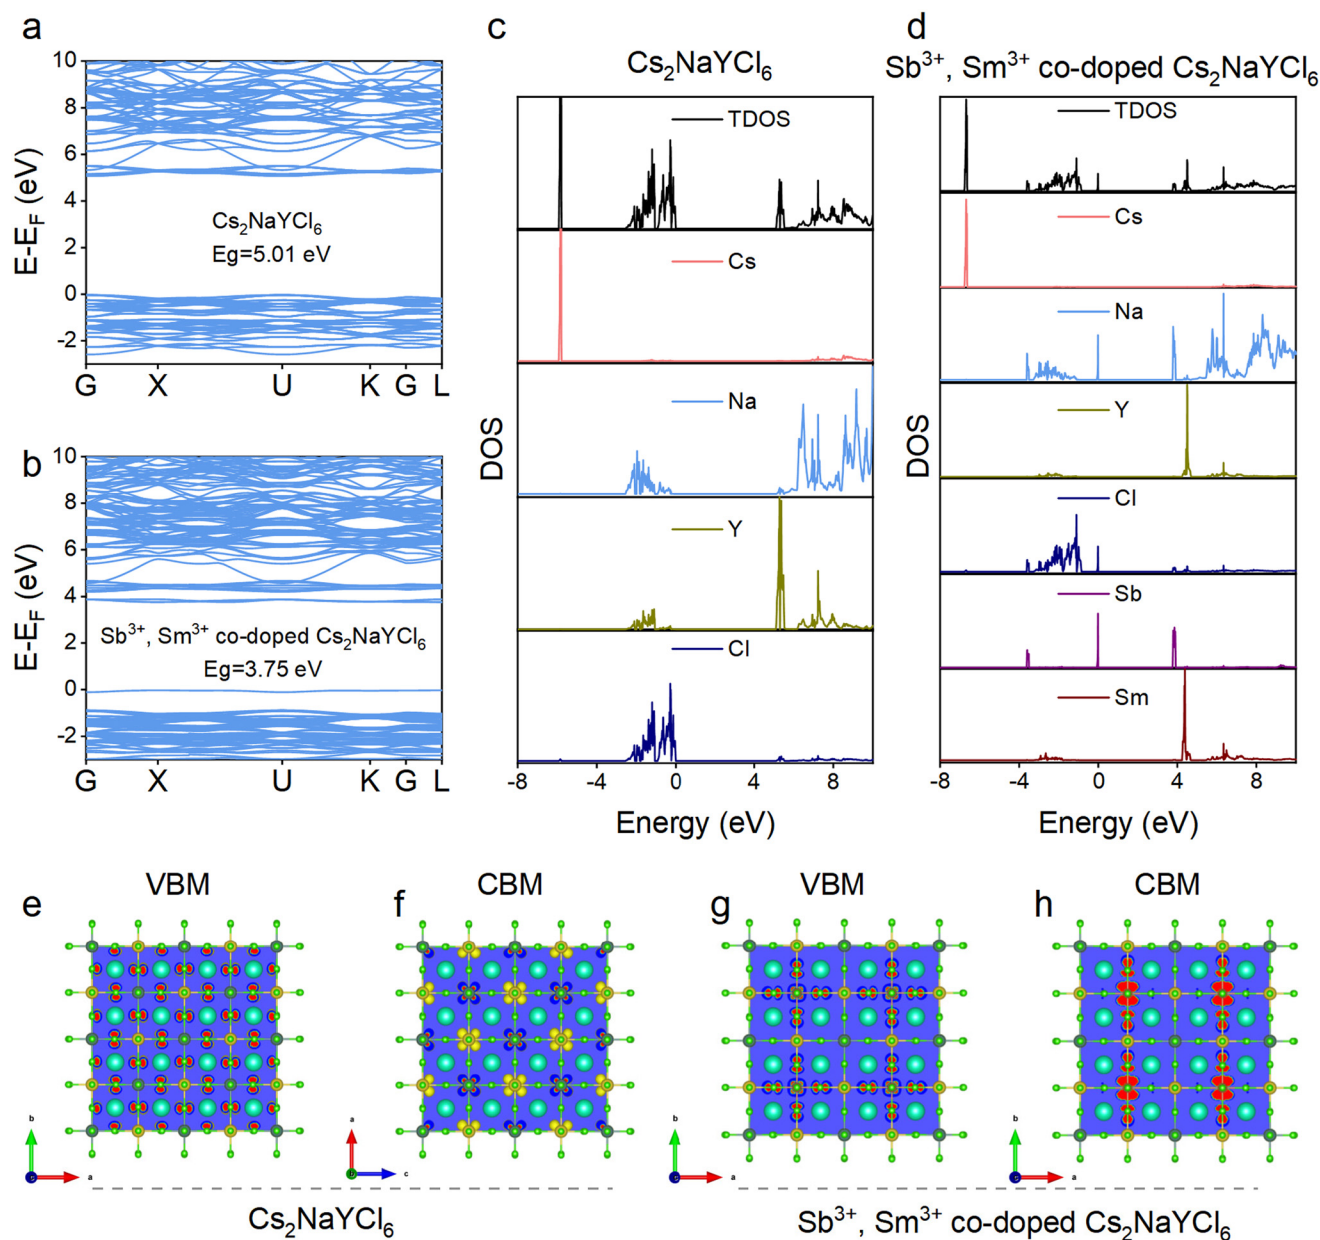

**Fig. 4** Calculated electronic band structures of  $\text{Cs}_2\text{NaYCl}_6$  (a) and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  (b). DOS of  $\text{Cs}_2\text{NaYCl}_6$  (c) and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  (d). Charge densities of  $\text{Cs}_2\text{NaYCl}_6$  (e and f) and  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  (g and h).

VBM of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  consisted of Sb 5s and Cl 3p states, and the CBM consisted of the Sb 5p state (Fig. 4d). Dopant s-electrons mainly contribute near the band edges of the host. So, the s-electron dopants ( $\text{Sb}^{3+}$ ) act as sensitizers and emitters. The charge density distribution of pristine  $\text{Cs}_2\text{NaYCl}_6$  reveals that the charge of the VBM is primarily concentrated around  $[\text{YCl}_6]^{3-}$  octahedra, as depicted in Fig. 4e. Conversely, the charge of the CBM is concentrated around Cl (Fig. 4f). The charge density distribution of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  reveals that the charge of the VBM is primarily concentrated around the  $[\text{YCl}_6]^{3-}$  octahedra (Fig. 4g). The charge of the CBM is concentrated around  $[\text{SbCl}_6]^{3-}$  octahedra (Fig. 4h).

To explore the potential applications of the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites, the stability of the samples in the environment was initially investigated. Fig. S12<sup>†</sup> presents a comparison of the XRD and PL spectra of the sample after one month with those of the fresh sample, demonstrating a good environmental stability at room temperature and a high humidity of 70%. Our samples were placed in a relatively high humidity environment (70%) for one month. From the XRD pattern, a NaCl impurity was observed, and the main diffraction peaks of the samples did not obviously change, which indicated that the samples were of high humidity stability and good humidity resistance. Fig. 5a demonstrates that the LED device, emitting cool white light,

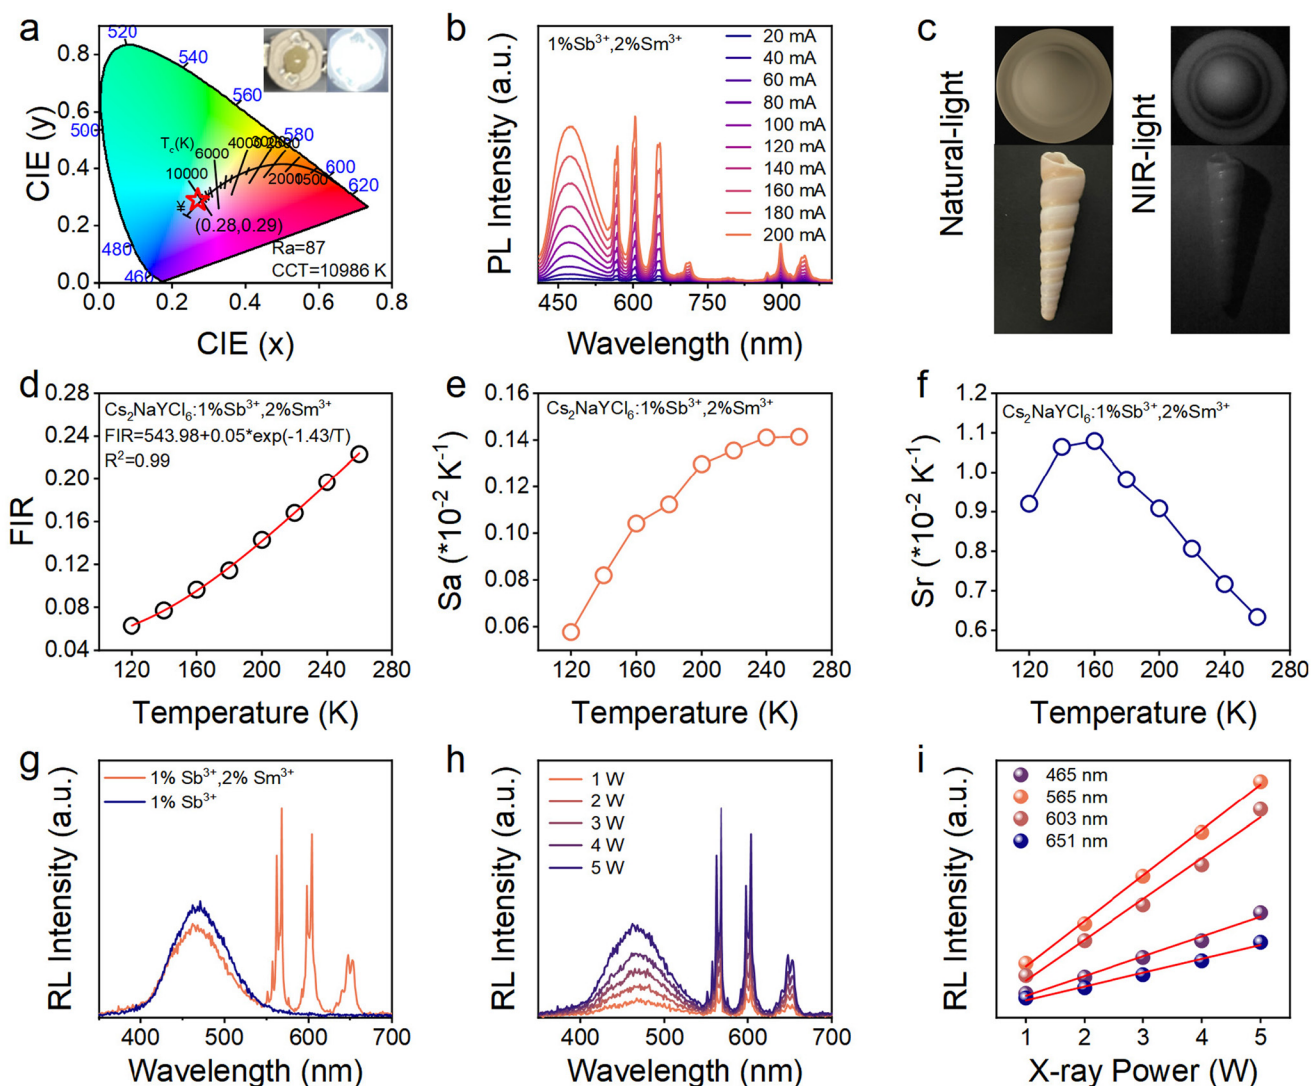

**Fig. 5** (a) CIE of 1%  $\text{Sb}^{3+}$ , 2%  $\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$ . (b) PL spectra of the 1%  $\text{Sb}^{3+}$ , 2%  $\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites under different currents. (c) Photos of a coffee cup lid and conch under natural and NIR light, respectively. FIR (d),  $S_a$  (e) and  $S_r$  (f) as functions of temperature. (g) RL spectra of the 1%  $\text{Sb}^{3+}$ , 2%  $\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites. (h) Variable power X-ray spectrum. (i) RL intensity variation with power at different emissions.

that was fabricated by integrating the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites with polymethylmethacrylate (PMMA) on a 365 nm UV chip, achieving a CRI of up to 87. The LED device exhibits a CIE of (0.28, 0.29) and a CCT of 10 986 K. Furthermore, the prepared LED lamp exhibited an excellent spectral stability across various currents ranging from 20 to 200 mA, as illustrated in Fig. 5b. Different imaging photographs of a conch and coffee cap under natural light irradiation and NIR light irradiation are depicted in Fig. 5c. Furthermore, the observation of different energy level transitions of  $\text{Sm}^{3+}$  with varying temperature sensitivities prompted us to explore the utilization of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  for temperature sensing. As shown in Fig. S13,† we observe a decrease in emission at 603 nm with increasing temperature within the range of 120–260 K, while the emission at 951 nm exhibits a positive cor-

relation within the same temperature range. This phenomenon suggests the potential use of the fluorescence intensity ratio (FIR) technique for precise temperature measurements. The relationship between temperature and FIR can be described by the following eqn (5):<sup>45</sup>

$$\text{FIR} = \frac{I_{951}}{I_{603}} = \frac{I_{0.951}}{I_{0.603}} \frac{1 + A_{951} \exp(-\Delta E_{951}/K_B T)}{1 + A_{604} \exp(-\Delta E_{603}/K_B T)} \approx B + C e^{-\Delta E/K_B T}, \quad (5)$$

where constants  $B$ ,  $C$  and  $\Delta E$  are related to the properties of  $\text{Sb}^{3+}/\text{Sm}^{3+}$ . Fig. 5d shows the relationship between FIR, calculated as  $I_{603 \text{ nm}}/I_{951 \text{ nm}}$  and experimental temperature  $T$ . It is noted that when the temperature rises from 120 to 260 K, the FIR value increases from 0.06 to 0.2. In the field of tempera-

ture sensing, absolute temperature sensitivity ( $S_a$ ) and relative temperature sensitivity ( $S_r$ ) are crucial factors to consider when assessing an optical temperature measurement. The values of ( $S_a$ ) and  $S_r$  can be calculated by eqn (6) and (7):<sup>46,47</sup>

$$S_a = \left| \frac{\partial \text{FIR}}{\partial T} \right| = Ce^{-\Delta E/K_B T} \times \frac{\Delta E}{K_B T^2} \quad (6)$$

$$S_r = 100\% \times \left| \frac{1}{\text{FIR}} \frac{\partial \text{FIR}}{\partial T} \right| = 100\% \times \frac{Ce^{-\Delta E/K_B T}}{B + Ce^{-\Delta E/K_B T}} \times \frac{\Delta E}{K_B T^2} \quad (7)$$

As shown in Fig. 5e and f, for the samples, the maximum values of  $S_a$  and  $S_r$  are 0.14 and 1.08%  $\text{K}^{-1}$ , respectively. In addition to the high sensitivity, the repeatability and stability of optical temperature measurements are also critical. Among the same type of rare-earth doped perovskites, the  $S_a$  and  $S_r$  values of optical temperature measurements in this work are among leading values (Table S2†). Temperature resolution ( $\delta T$ ) is another important parameter to evaluate the performance of optical thermometry, which can be expressed as follows:

$$\delta T = \frac{1}{S_r} \frac{\Delta \text{FIR}}{\text{FIR}} \quad (8)$$

In this case,  $\Delta \text{FIR}/\text{FIR}$  stands for the relative error in the measurement process, and its value is approximately 0.5%.<sup>47,48</sup> Hence, it is calculated that the minimum temperature resolution is 0.46 at 160 K. At the same time, the non-contact optical thermometry of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  has a good repeatability. The above results indicate that  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  is a potential material for non-contact optical thermometers. Additionally,  $\text{Sb}^{3+}:\text{Cs}_2\text{NaYCl}_6$  and the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites exhibit light emission under excitation by high-energy X-rays, as depicted in Fig. 5g. We conducted experiments at various X-ray power intensities to establish the relationship between emission and X-ray intensity. Notably, the radioluminescence (RL) intensity of  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  displays a linear correlation with the power of X-rays, as illustrated in Fig. 5h and i.

### 3. Conclusions

In summary, the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  rare-earth double perovskites with a tunable emission and excellent stability were synthesized *via* a solvothermal method. It was found that the transition of  $^3\text{P}_1 \rightarrow ^1\text{S}_0$  could be split into two transitions due to the Jahn-Teller effect, resulting in a double STE emission within a temperature range of 80 to 260 K. However, as the temperature increases, the excited electrons tend to move toward a higher energy STE emission, leading to the disappearance of the low-energy STE emission within the same temperature range (80–260 K). By adjusting the  $\text{Sm}^{3+}$  feeding concentration, we were able to adjust the energy transfer efficiency between STE and  $\text{Sm}^{3+}$  emissions. Furthermore, the  $\text{Sb}^{3+}/\text{Sm}^{3+}$  co-doped  $\text{Cs}_2\text{NaYCl}_6$  double perovskites exhibited multifunctional applications in high-energy X-rays and

night vision. These double perovskites possess excellent optical properties and stability, rendering them promising candidates for applications in white-light illumination and temperature sensing.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgements

This work was supported by the National Natural Science Foundation of China (Grant No. 52162021 and 22175043), Open Foundation of State Key Laboratory of Featured Metal Materials and Life-cycle Safety for Composite Structures (Grant No. MMCS2023OF05), and Guangxi Science and Technology Plan Project (Guike AA23073018). The calculation was supported by the high-performance computing platform of Guangxi University.

### References

- 1 Y. Bao, H. Wang, M. An, H. Tang, J. Li, J. Li, C. Tan, Y. Luo, J. Xu and Y. Yang, Defect-modulated synthesis and optoelectronic properties in chemical vapor deposited  $\text{CsPbBr}_3$  microplates, *Nano Res.*, 2024, **17**, 4610–4615.
- 2 Y. Jiang, C. Sun, J. Xu, S. Li, M. Cui, X. Fu, Y. Liu, Y. Liu, H. Wan, K. Wei, T. Zhou, W. Zhang, Y. Yang, J. Yang, C. Qin, S. Gao, J. Pan, Y. Liu, S. Hoogland, E. H. Sargent, J. Chen and M. Yuan, Synthesis-on-substrate of quantum dot solids, *Nature*, 2022, **612**, 679–684.
- 3 M. Cui, C. Qin, Z. Zhou, Y. Jiang, S. Zhang, Z. Yuan, M. Yuan, K. Yu, Y. Jiang and Y. Liu, Tuning coherent phonon dynamics in two-dimensional phenylethylammonium lead bromide perovskites, *Nano Res.*, 2023, **16**, 3408–3414.
- 4 C. Zhao, C. Zhu, Y. Yu, W. Xue, X. Liu, F. Yuan, J. Dai, S. Wang, B. Jiao and Z. Wu, Multifunctional short-chain 2-thiophenealkylammonium bromide ligand-assisted perovskite quantum dots for efficient light-emitting diodes, *ACS Appl. Mater. Interfaces*, 2023, **15**, 40080–40087.
- 5 X. Hu, Y. Xu, J. Wang, J. Ma, L. Wang and W. Jiang, Ligand-modified synthesis of shape-controllable and highly luminescent  $\text{CsPbBr}_3$  perovskite nanocrystals under ambient conditions, *Inorg. Chem. Front.*, 2022, **9**, 6080–6090.
- 6 Q. Lin, S. Bernardi, B. Shabbir, Q. Ou, M. Wang, W. Yin, S. Liu, A. S. R. Chesman, S. O. Furer, G. Si, N. Medhekar, J. Jasieniak, A. Widmer-Cooper, W. Mao and U. Bach, Phase-control of single-crystalline inorganic halide perovskites via molecular coordination engineering, *Adv. Funct. Mater.*, 2022, **32**, 2109442.
- 7 Y. Xie, A. Zhou, X. Zhang, Q. Ou and S. Zhang, Metal cation substitution of halide perovskite nanocrystals, *Nano Res.*, 2022, **15**, 6522–6550.

- 8 R. Zeng, L. Zhang, Y. Xue, B. Ke, Z. Zhao, D. Huang, Q. Wei, W. Zhou and B. Zou, Highly efficient blue emission from self-trapped excitons in stable  $\text{Sb}^{3+}$ -doped  $\text{Cs}_2\text{NaInCl}_6$  double perovskites, *J. Phys. Chem. Lett.*, 2020, **11**, 2053–2061.
- 9 Z. Xiao, K. Du, W. Meng, J. Wang, D. B. Mitzi and Y. Yan, Intrinsic instability of  $\text{Cs}_2\text{In}(\text{I})\text{M}(\text{III})\text{X}_6$  ( $\text{M} = \text{Bi}, \text{Sb}$ ;  $\text{X} = \text{Halogen}$ ) double perovskites: a combined density functional theory and experimental study, *J. Am. Chem. Soc.*, 2017, **139**, 6054–6057.
- 10 D. Li, J. Song, Y. Cheng, X. Wu, Y. Wang, C. Sun, C. Yue and X. Lei, Ultra-sensitive, selective and repeatable fluorescence sensor for methanol based on a highly emissive 0D hybrid lead-free perovskite, *Angew. Chem., Int. Ed.*, 2022, **61**, e202206437.
- 11 Z. Chen, F. Zhang, D. Yang, H. Ji, X. Chen, D. Wu, X. Li, Y. Zhang and Z. Shi, Doping suppresses lattice distortion of vacant quadruple perovskites to activate self-trapped excitons emission, *Nano Res.*, 2024, **17**, 3068–3078.
- 12 S. Wu and Y. Liu, Recent advancements and manipulation strategies of colloidal  $\text{Cs}_2\text{BIBiX}_6$  lead-free halide double perovskite nanocrystals, *Nano Res.*, 2023, **16**, 5572–5591.
- 13 H. Yang, X. Chen, Y. Chu, C. Sun, H. Lu, M. Yuan, Y. Zhang, G. Long, L. Zhang and X. Li, A universal hydrochloric acid-assistant powder-to-powder strategy for quick and mass preparation of lead-free perovskite microcrystals, *Light: Sci. Appl.*, 2023, **12**, 75.
- 14 C. Wang, J. Xiao, Z. Yan, X. Niu, T. Lin, Y. Zhou, J. Li and X. Han, Colloidal synthesis and phase transformation of all-inorganic bismuth halide perovskite nanoplates, *Nano Res.*, 2023, **16**, 1703–1711.
- 15 A. Huang, M. Liu, C. Duan, K. Wong and P. A. Tanner, Understanding the ultraviolet, green, red, near infrared and infrared emission properties of bismuth halide double perovskite, *Inorg. Chem. Front.*, 2022, **9**, 6379–6390.
- 16 J. Luo, X. Wang, S. Li, J. Liu, Y. Guo, G. Niu, L. Yao, Y. Fu, L. Gao, Q. Dong, C. Zhao, M. Leng, F. Ma, W. Liang, L. Wang, S. Jin, J. Han, L. Zhang, J. Etheridge, J. Wang, Y. Yan, E. H. Sargent and J. Tang, Efficient and stable emission of warm-white light from lead-free halide double perovskites, *Nature*, 2018, **563**, 541–545.
- 17 S. Bao, H. Yu, G. Gao, H. Zhu, D. Wang, P. Zhu and G. Wang, Rare-earth single atom based luminescent composite nanomaterials: tunable full-color single phosphor and applications in WLEDs, *Nano Res.*, 2022, **15**, 3594–3605.
- 18 Y. Chen, R. Zeng, Q. Wei, S. Zhang, B. Luo, C. Chen, X. Zhu, S. Cao, B. Zou and J. Z. Zhang, Competing energy transfer-modulated dual emission in  $\text{Mn}^{2+}$ -doped  $\text{Cs}_2\text{NaTbCl}_6$  rare-earth double perovskites, *J. Phys. Chem. Lett.*, 2022, **13**, 8529–8536.
- 19 H. Wang, J. Yao, Q. Wei, J. Zhao, B. Zou and R. Zeng, Simultaneously achieving multicolor emission of downshifting and up-conversion in  $\text{Yb}^{3+}$ ,  $\text{Er}^{3+}$ -codoped  $\text{Cs}_2\text{NaGdCl}_6$  double perovskites, *Adv. Opt. Mater.*, 2023, **11**, 2300694.
- 20 Y. Liu, F. Di Stasio, C. Bi, J. Zhang, Z. Xia, Z. Shi and L. Manna, Near-infrared light emitting metal halides: materials, mechanisms, and applications, *Adv. Mater.*, 2024, 2312482.
- 21 Y. Huang, Y. Pan, C. Peng, Y. Ding, H. Lian, L. Li and J. Lin, Orange/cyan emissive sensors of  $\text{Sb}^{3+}$  for probing water via reversible phase transformation in rare-earth-based perovskite crystals, *Inorg. Chem. Front.*, 2023, **10**, 991–1000.
- 22 Y. Hua, T. Wang, J. S. Yu, W. Ran and L. Li, Modulating A site compositions of europium(III)-doped double-perovskite niobate phosphors, *Inorg. Chem. Front.*, 2022, **9**, 6211–6224.
- 23 L. Zhang and M. Yuan, Lanthanide doped lead-free double perovskites as the promising next generation ultra-broad-band light sources, *Light: Sci. Appl.*, 2022, **11**, 99.
- 24 Y. Wang, P. Dang, L. Qiu, G. Zhang, D. Liu, Y. Wei, H. Lian, G. Li, Z. Cheng and J. Lin, Multimode luminescence tailoring and improvement of  $\text{Cs}_2\text{NaHoCl}_6$  cryolite crystals via  $\text{Sb}^{3+}/\text{Yb}^{3+}$  alloying for versatile photoelectric applications, *Angew. Chem., Int. Ed.*, 2023, **62**, e202311699.
- 25 Z. Rao, M. Cao, Z. Chen, X. Zhao and X. Gong, Understanding and effective tuning of red-to-green upconversion emission in Ho-based halide double perovskite microcrystals, *Adv. Funct. Mater.*, 2024, **34**, 2311568.
- 26 D. Chen, X. Zhang, J. Wei, L. Zhou, P. Chen, Q. Pang and J. Z. Zhang, Simultaneous enhancement of near infrared luminescence and stability of  $\text{Cs}_2\text{AgInCl}_6:\text{Cr}^{3+}$  double perovskite single crystals enabled by a  $\text{Yb}^{3+}$  dopant, *Inorg. Chem. Front.*, 2022, **9**, 4695–4704.
- 27 Y. Liu, X. Rong, M. Li, M. S. Molokeev, J. Zhao and Z. Xia, Incorporating rare-earth Terbium(III) ions into  $\text{Cs}_2\text{AgInCl}_6$ : Bi nanocrystals toward tunable photoluminescence, *Angew. Chem., Int. Ed.*, 2020, **59**, 11634–11640.
- 28 S. Li, Q. Hu, J. Luo, T. Jin, J. Liu, J. Li, Z. Tan, Y. Han, Z. Zheng, T. Zhai, H. Song, L. Gao, G. Niu and J. Tang, Self-Trapped Exciton to Dopant Energy Transfer in Rare Earth Doped Lead-Free Double Perovskite, *Adv. Opt. Mater.*, 2019, **7**, 1901098.
- 29 P. Zhu, S. Thapa, H. Zhu, S. Wheat, Y. Yue and D. Venugopal, Composition engineering of lead-free double perovskites towards efficient warm white light emission for health and well-being, *J. Alloys Compd.*, 2023, **960**, 170836.
- 30 X. Li, X. Shen, M. Lu, J. Wu, Y. Zhong, Z. Wu, W. W. Yu, Y. Gao, J. Hu, J. Zhu, Y. Zhang and X. Bai, Wide-coverage and efficient NIR emission from single-component nanophosphors through shaping multiple metal-halide packages, *Angew. Chem., Int. Ed.*, 2023, **62**, e202217832.
- 31 R. Tang, Y. Yang, Y. Yang, X. Ouyang, J. Che, S. Chen, X. Yao, B. Deng and R. Yu, A novel reddish-orange emitting  $\text{NaSrBiTeO}_6:\text{Sm}^{3+}$  phosphor with high moisture resistance and thermostability for horticultural light emitting diode applications, *J. Am. Ceram. Soc.*, 2024, **107**, 3012–3027.
- 32 S. K. Cushing, M. Li, F. Huang and N. Wu, Origin of strong excitation wavelength dependent fluorescence of graphene oxide, *ACS Nano*, 2014, **8**, 1002–1013.

- 33 J. Nie, H. Li, S. Fang, B. Zhou, Z. Liu, F. Chen, Y. Wang and Y. Shi, Efficient red photoluminescence in holmium-doped  $\text{Cs}_2\text{NaInCl}_6$  double perovskite, *Cell Rep. Phys. Sci.*, 2022, **3**, 100820.
- 34 J. Li, Z. Tan, M. Hu, C. Chen, J. Luo, S. Li, L. Gao, Z. Xiao, G. Niu and J. Tang, Antimony doped  $\text{Cs}_2\text{SnCl}_6$  with bright and stable emission, *Front. Optoelectron.*, 2019, **12**, 352–364.
- 35 Y. Jing, Y. Liu, M. Li and Z. Xia, Photoluminescence of singlet/triplet self-trapped excitons in  $\text{Sb}^{3+}$ -based metal halides, *Adv. Opt. Mater.*, 2021, **9**, 2002213.
- 36 H. Arfin, A. S. Kshirsagar, J. Kaur, B. Mondal, Z. Xia, S. Chakraborty and A. Nag,  $ns^2$  electron ( $\text{Bi}^{3+}$  and  $\text{Sb}^{3+}$ ) doping in lead-free metal halide perovskite derivatives, *Chem. Mater.*, 2020, **32**, 10255–10267.
- 37 Y. Jing, Y. Liu, X. Jiang, M. S. Molokeev, Z. Lin and Z. Xia,  $\text{Sb}^{3+}$  dopant and halogen substitution triggered highly efficient and tunable emission in lead-free metal halide single crystals, *Chem. Mater.*, 2020, **32**, 5327–5334.
- 38 A. Shinde, R. Gahlaut and S. Mahamuni, Low-temperature photoluminescence studies of  $\text{CsPbBr}_3$  quantum dots, *J. Phys. Chem. C*, 2017, **121**, 14872–14878.
- 39 J. Ghosh, L. P. L. Mawlong, M. G. B. A. J. Pattison, W. Theis, S. Chakraborty and P. K. Giri, Solid-state synthesis of stable and color tunable cesium lead halide perovskite nanocrystals and the mechanism of high-performance photodetection in a monolayer  $\text{MoS}_2/\text{CsPbBr}_3$  vertical heterojunction, *J. Mater. Chem. C*, 2020, **8**, 8917–8934.
- 40 Z. Tan, Y. Chu, J. Chen, J. Li, G. Ji, G. Niu, L. Gao, Z. Xiao and J. Tang, Lead-free perovskite variant solid solutions  $\text{Cs}_2\text{Sn}_{1-x}\text{Te}_x\text{Cl}_6$ : bright luminescence and high anti-water stability, *Adv. Mater.*, 2020, **32**, 2002443.
- 41 D. Zhu, M. L. Zaffalon, J. Zito, F. Cova, F. Meinardi, L. De Trizio, I. Infante, S. Brovelli and L. Manna, Sb-doped metal halide nanocrystals: a 0D versus 3D comparison, *ACS Energy Lett.*, 2021, **6**, 2283–2292.
- 42 B. Zhou, Z. Liu, S. Fang, H. Zhong, B. Tian, Y. Wang, H. Li, H. Hu and Y. Shi, Efficient white photoluminescence from self-trapped excitons in  $\text{Sb}^{3+}/\text{Bi}^{3+}$ -codoped  $\text{Cs}_2\text{NaInCl}_6$  double perovskites with tunable dual-emission, *ACS Energy Lett.*, 2021, **6**, 3343–3351.
- 43 W. Zhang, J. Wei, Z. Gong, P. Huang, J. Xu, R. Li, S. Yu, X. Cheng, W. Zheng and X. Chen, Unveiling the excited-state dynamics of  $\text{Mn}^{2+}$  in 0D  $\text{Cs}_4\text{PbCl}_6$  perovskite nanocrystals, *Adv. Sci.*, 2020, **7**, 2002210.
- 44 T. Chang, H. Wang, Y. Gao, S. Cao, J. Zhao, B. Zou and R. Zeng, Component engineering to tailor the structure and optical properties of Sb-doped Indium-based halides, *Inorg. Chem.*, 2022, **61**, 1486–1494.
- 45 J. Xue, M. Song, H. M. Noh, S. H. Park, B. R. Lee, J. H. Kim and J. H. Jeong, Near-ultraviolet light induced red emission in  $\text{Sm}^{3+}$ -activated  $\text{NaSrLa}(\text{MoO}_4)_3$  phosphors for solid-state illumination, *J. Alloys Compd.*, 2020, **817**, 152705.
- 46 W. Li, S. Wu, H. Zhang, X. Zhang, J. Zhuang, C. Hu, Y. Liu, B. Lei, L. Ma and X. Wang, Enhanced biological photosynthetic efficiency using light-harvesting engineering with dual-emissive carbon dots, *Adv. Funct. Mater.*, 2018, **28**, 1804004.
- 47 X. Li, D. Wang, Y. Zhong, F. Jiang, D. Zhao, S. Sun, P. Lu, M. Lu, Z. Wang, Z. Wu, Y. Gao, Y. Zhang, W. W. Yu and X. Bai, Halide double perovskite nanocrystals doped with rare-earth ions for multifunctional applications, *Adv. Sci.*, 2023, **10**, 2207571.
- 48 A. Zhang, Z. Sun, M. Jia, Z. Fu, B. C. Choi, J. H. Jeong and S. H. Park,  $\text{Sm}^{3+}$ -doped niobate orange-red phosphors with a double-perovskite structure for plant cultivation and temperature sensing, *J. Alloys Compd.*, 2021, **889**, 161671.