

Polymer Chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. Pusse, S. Heinz, W. Limprasart, L. Gemmer, S. Witayakran, S. Schabel, V. Presser, T. Gutmann and M. Gallei, *Polym. Chem.*, 2026, DOI: 10.1039/D5PY01203A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Development and Modification of Porous Polymer Structures in the Vicinity of Cellulose Fibers

Sebastian Pusse¹, Sebastian Heinz¹, Waranya Limprasart², Lea Gemmer¹, Suteera Witayakran^{1,4}, Samuel Schabeß, Volker Presser^{5,6,7}, Torsten Gutmann^{2,8} and Markus Gallei^{1,7*}*

¹Polymer Chemistry, Saarland University, Campus C4 2, 66123 Saarbrücken, Germany

² Eduart-Zintl-Institute for Inorg. and Phys. Chemistry, Technical University Darmstadt, Peter-Grünberg-Straße 8, 64287 Darmstadt, Germany³ Mechanical Engineering, Chair of Paper Technology and Mechanical Process Engineering, Technical University of Darmstadt, Alexanderstraße 8, Darmstadt, 64283, Germany

⁴Max Planck Institute for Informatics, Saarland Informatics Campus, E1 4, 66123 Saarbrücken, Germany 66123, Germany

⁵ INM - Leibniz Institute for New Materials, Saarbrücken 66123, Germany.

⁶Department of Materials Science and Engineering, Saarland University, Campus D2 2, Saarbrücken 66123, Germany

⁷Saarene, Saarland Center for Energy Materials and Sustainability, Saarland University, Campus C4 2, 66123 Saarbrücken, Germany

⁸ Department of Chemistry, Physical Chemistry, University of Paderborn, Warburger Straße 100, 33098 Paderborn, Germany



KEYWORDS: amphiphilic block copolymers; self-assembly; membranes; post-modification; porous materials; cellulose; fibers; functional paper sheet

ABSTRACT:

In this work, hierarchically porous materials have been prepared by the self-assembly and pore formation of different amphiphilic block copolymers (BCPs) in the vicinity of cellulose paper sheets. For this, polystyrene-*block*-polysolketal methacrylate (PS-*b*-SMA) as a linear BCP and polymethyl methacrylate-*block*-polysolketal methacrylate (PMMA-*b*-SMA)_n as a star-shaped BCP were prepared using living anionic polymerization. Under a mild acidic environment, the amphiphilic properties were revealed by converting the PSMA block segment to poly(dihydroxypropyl methacrylate) (PDHMPA). The BCPs were incorporated onto the Linter's fiber-based cellulose sheets by a self-assembly and nonsolvent-induced phase separation (SNIPS) process. The received porous materials have been further modified with 3-aminopropyltriethoxysilane (APTES) and 3,3,3-trifluoropropyl dimethyl chlorosilane (TFPCS) using vapor-phase modification. This strategy enabled tuning the surface properties of the porous structures received to adjust surface polarity further. The characteristics of the porous modified materials were confirmed at the microscopic scale by solid-state nuclear magnetic resonance (NMR) combined with selectively enhanced dynamic nuclear polarization (DNP), and Fourier transform infrared (FTIR) spectroscopy. The influence of APTES and TFPCS was further analyzed at the macroscopic level using water contact angle (WCA) measurements and water permeance testing, in which changes were observed for both modifiers. Using this convenient strategy, the fabrication of functional porous cellulose composite materials is demonstrated, paving the way for a new family of cellulose-based porous materials.



INTRODUCTION

The availability of freshwater is becoming a global challenge for humankind, with up to 87 of 180 countries expected to face water scarcity by 2050. Yet, the small amount of fresh drinking water is further reduced by (human-made) contamination. To mention two very recent examples that have only gained significant attention in recent years, one is the pollution of our environment by microplastics and the health concerns it raises.¹⁻⁴ The second example would be per- and polyfluoroalkyl substances (PFAS) due to their high persistence in the environment and the human body.⁵⁻⁷ To fight against such health hazards, an ever-increasing range of tools is required now and in the future. One approach to addressing environmental pollution is the use of porous functional materials.⁸⁻¹⁰ Such porous materials are used in filtration and adsorption systems and applications, and are often composed of polyvinyl difluoride (PVDF), polyacrylonitrile (PAN), polyether sulfones (PES), polyamide (PA), or cellulose.¹¹⁻¹³ The last example is considered more sustainable, as it is derived from natural and renewable resources such as wood, cotton, hemp, algae, and bacteria, rather than petroleum-sourced products.

Cellulose, the most abundant renewable biopolymer on earth, is a linear polysaccharide composed of β (1 $\rightarrow$ 4)-linked D-glucose units biosynthesized by plants, various types of algae, and bacteria.¹⁴ Due to its renewability, biodegradability, and beneficial mechanical properties, cellulose has become a sustainable alternative to petroleum-based polymers in materials science and engineering, helping reduce environmental impacts and decrease reliance on non-renewable resources.¹⁵ Because cellulose fibers are lightweight, possess high tensile strength and exhibit good thermal stability, these qualities make them valuable for manufacturing paper and packaging, textiles, films, membranes bio composites and emerging technologies such as biomedical devices and smart electronics.^{16, 17} However, the intrinsic hydrophilicity of cellulose, caused by the abundance of surface hydroxy moieties in its backbone, limits its compatibility



with hydrophobic matrices and hampers performance in humid conditions. To overcome these challenges, surface modification has been widely studied to improve or tailor interfacial, chemical, wettability, and barrier properties to meet the desired requirements of advanced materials. Various surface modification techniques have been developed, including chemical grafting, silanization, polymer grafting, plasma or vapor deposition and surface coating.^{14, 18, 19} Among these, polymer coating has gained significant attention due to its simplicity, scalability and ability to preserve the native structure of the fiber substrate.^{20, 21} Applying functional polymer layers onto cellulose fibers or paper allows for adjustments in surface wettability, barrier properties and mechanical strength, making it suitable for application such as sustainable packaging,²² filtration membranes,²³ microfluids,²⁴ sensors,^{25, 26} and advanced functional composites.^{27, 28} Besides improving the intrinsic properties of cellulose fibers or paper, the coating process can also benefit from the presence of the cellulose substrate itself. Recent studies have shown that the cellulose substrate has a potential impact on molecular alignment or enhances the structural organization to produce highly ordered microstructures of amphiphilic block copolymers (BCP), such as polystyrene-*block*-poly(2-hydroxyethyl methacrylate) (PS-*b*-PHEMA)²⁹ and polyisoprene-*block*-polyvinyl pyridines (PI-*b*-P2VP),³⁰ in direct contact with cellulose fibers. The self-assembly of BCPs, such as PS-*b*-PHEMA or PI-*b*-P2VP, was strongly influenced by the presence of cellulose fibers, thereby affecting domain orientation and pore-forming capabilities. By combining a wide range of BCPs with specific functionalities, the applicability of porous cellulose materials can be significantly enhanced. For example, cellulose can be equipped with BCPs, which not only provide a hierarchical porous structure but also feature stimuli responsiveness. Temperature as a trigger was shown to alter pore size and polarity in so-called smart membranes.^{31, 32} A change in a membrane characteristic can be obtained as a response to changes in the pH of a filtrate,³³⁻³⁵ or the presence of sugars.³⁶ BCP can be used not only for the fabrication of stimuli-responsive membranes but also for targeting specific pollutants, such as heavy ions or



perfluorinated pollutants.³⁷ For each example presented, the functionality is already implemented into the polymer before membrane fabrication. For functionalities that interfere with the membrane-forming process or cannot be polymerized and integrated into the BCP segments, an alternative approach to application-specific membranes is the post-modification of already prepared BCP membranes. When a direct synthesis or membrane preparation is not suitable, a BCP with an addressable functional group is synthesized, converted into a membrane, and then postmodified. Membranes derived from the self-assembly of polystyrene-*block*-poly(4-vinylpyridine) (PS-*b*-P4VP) represent a feasible polymer system for post-modification strategies. Here, the P4VP block segment can be modified to form a polyelectrolyte brush, enhancing anti-fouling properties.³⁸ The already mentioned PS-*b*-PHEMA represents another family of BCP motifs. PHEMA provides hydroxy groups as addressable functional groups. These groups already impart anti-fouling properties^{39, 40} but also allow further modification with amines, peptides⁴¹ or esters⁴² for protein-selective separation strategies. In all the examples presented before, the membranes originate from a special procedure, namely the self-assembly and non-solvent induced phase separation (SNIPS) process.^{43, 44} The SNIPS process represents a very feasible tool for the fabrication of such high-performance membranes, where pore size can be defined by the material that is used in membrane preparation.⁴⁵ Ultrafiltration membranes with a uniform pore-size distribution, combined with high pore order and pore density, provide a sharp cutoff for filtrates, forming the foundation here. The BCP is a central element in this fabrication protocol. To produce such uniform membranes, tailored BCPs serve as the basis for their composition and architecture. To approach such materials, controlled radical polymerizations⁴⁶⁻⁵⁰ as well as living anionic polymerization^{37, 41, 51-53} play a crucial role in material preparation. These controlled polymerization techniques can not only be used for the synthesis of linear block copolymers. They also allow a wide variety of block copolymer architectures. Here, the architectures of star-shaped block copolymers in the form of (AB)_n, with n indicating the number of arms,



are of special interest. Influenced by BCP architecture, gyroidal morphology becomes more stable over a wider range of BCP-compositions⁵⁴⁻⁵⁷ compared to a rather narrow section of the Mean-Field diagram for a common linear block copolymer.⁵⁸ Based on that observation, the application of star-shaped BCPs can lead to an alternative structure of the surface layer of a SNIPS membrane. Instead of dense hexagonally packed cylindrical pores in the top layer,⁴³ which must be trapped kinetically,⁵⁹ interconnected porous structures with an isotropic orientation can be introduced using star-shaped block copolymers. Such structures tend to allow a higher water flux.^{60, 61}

In this work, we prepared two types of amphiphilic block copolymers via living anionic polymerization. First, a polystyrene-*block*-poly(2,3-dihydroxypropyl methacrylate) PS-*b*-PDHPMA BCP was prepared using solketal methacrylate (SMA) as a precursor for DHPMA. The second developed polymer was an amphiphilic star-shaped BCP prepared via a convergent arm-first route. For the more hydrophobic major block, methyl methacrylate (MMA) is used. The second, minor block is based again on SMA. The more hydrophilic character is again revealed during the deprotection step of the PMMA-*b*-PSMA block copolymer, converting into PMMA-*b*-PDHPMA. Both polymers were fabricated into asymmetric porous structures using the SNIPS process and modified further with (3-aminopropyl) triethoxysilane APTES and 3,3,3-trifluoropropyl dimethyl chlorosilane (TFPCS) via vapor phase reactions. Both membranes were characterized using FTIR spectroscopy and water contact angle measurements. These were further complemented by selectively enhanced dynamic nuclear polarization (DNP) solid-state NMR spectroscopy, which has been established as a powerful tool to specifically address structural moieties at a molecular level in highly complex paper/polymer hybrid materials.^{62, 63} In the final step, the effect of surface modification on the membrane's water permeance was investigated.



EXPERIMENTAL SECTION

Materials

All chemicals and solvents were purchased from TCI chemicals, Sigma-Aldrich, Fisher Scientific, or BLD Pharma. All chemicals and solvents were used as received unless otherwise stated. All monomers were prepared according to standard procedures typical for anionic polymerization. The monomers were dried over CaH_2 and distilled over prior to use. Tetrahydrofuran (THF) was dried with diphenyl hexyllithium (DPHLi) and transferred freshly into a reaction ampulla using cryotransfer. MeOH used for quenching of active chain ends was dried over molecular sieve ($3\text{\AA}$) before cryotransfer and storage in a glovebox. The monomer SMA was synthesized as described in the literature, using toluene as a solvent instead of benzene.⁶⁴ Linters papers with a weight of $50.0 \pm 1.6 \text{ g m}^{-2}$ were prepared by the Chair of Paper Technology and Mechanical Process Engineering PMV, following the Rapid-Köthen paper sheet formation procedure.

Polymer Synthesis

*Linear Block Copolymer PS-*b*-PSMA (PS-*b*-PDHPMA)*

To an ampulla containing freshly distilled THF, catalytic amounts of LiCl were added, and the mixture was titrated with *s*-BuLi (80 μL) and stirred overnight at room temperature. The following day, the ampulla was cooled to $-73\text{ }^\circ\text{C}$. Styrene (1.80 mL, 1825 eq.) was added, and the rapid addition of *s*-BuLi (8 μL , 1.0 eq.) initiated the polymerization. The solution turned orange immediately. After 3.5 h, 1,1-Diphenylethylene (DPE) (4 μL , 2.0 eq.) was added, and the mixture was stirred at room temperature for 30 min. The solution turned dark red immediately after DPE addition. After cooling down to $-73\text{ }^\circ\text{C}$, SMA (0.54 mL, 250 eq.) was added to the ampulla and stirred overnight. After that, the active polymer chains were quenched by the rapid addition of 10 μL of MeOH. The BCP was precipitated in MeOH. After drying



under reduced pressure at 40 °C, the product (1.78 g) was dissolved in THF (40 mL). To the solution, hydrochloric acid (3 mL, 2 M) was added, and the mixture was stirred overnight at room temperature. The polymer was precipitated from water afterward. The deprotected block copolymer was received as a white powder (1.71g) after drying under reduced pressure at 40 °C for 3 h.

*Star Block Copolymer (PMMA-*b*-PSMA)_n ((PMMA-*b*-PDHPMA)_n)*

To an ampulla containing freshly distilled THF, catalytic amounts of LiCl were added. The solution was titrated with *s*-BuLi (80 µL) and stirred overnight at room temperature. The following day, 2 mL of the solution was transferred to the ampulla, which was cooled to -73 °C. After cooling down, SMA (0.6 mL, 154.0 eq.) was added. The second vessel was cooled to 4 °C. After cooling down, DPE (0.011 mL, 3.1 eq.), followed by *s*-BuLi (10 µL, 1 eq.), was added to the second vessel. The solution turned dark red immediately. Polymerization was initiated by adding DPHLi to the ampulla. The following day, MMA (2.35 mL, 1100 eq.) was added and again stored at -73 °C for three hours. In the next step, 1,4-butanediol methacrylate (BDDMA) (0.044 mL, 10.5 eq.) was added, and the reaction was continued for another 4.5 h at -73 °C. The polymerization was stopped by adding MeOH (10 µL). The polymer was precipitated in n-hexane. After drying under reduced pressure at 40 °C, the product (2.16 g) was dissolved in THF (100 mL). To the solution, hydrochloric acid (6 mL, 2 M) was added, and the mixture was stirred overnight at room temperature. The polymer was precipitated from water afterward. The deprotected block copolymer was received as a white powder (2.09 g) after drying under reduced pressure at 40 °C for 3 h.

Protection of Hydroxy Moieties with Benzoic Anhydride Bz₂O

For the introduction of benzoic moieties as a protecting group a protocol was applied already presented elsewhere.⁵² First 27.6 mg of the linear BCP PS-*b*-PDHPMA, respectively 27.9 mg of the star-shaped



BCP (PMMA-*b*-PDHPMA)_n was dissolved in 2 ml pyridine each in a round-bottom flask. Then, to each reaction vessel, 900 mg of Bz₂O was added and stirred for 72h. The linear BCP was precipitated in MeOH, while the star-shaped BCP was precipitated in *n*-hexane. The Bz-protected BCP was received as a white powder (15.1 mg). The Bz-protected star-shaped BCP was received as a white powder as well (16.6 mg).

Membrane Formation via SNIPS protocol

In the first step of the membrane preparation process, a solvent mixture was prepared as a stock solution, containing THF, dimethylformamide (DMF), and 1,4-dioxane (DOX) in a weight ratio of 2:1:1. For each polymer, a casting solution was prepared by combining the polymer, the solvent mixture, and additives listed in **Tables S1, S3 and S5**. To ensure complete polymer dissolution, the mixture was slowly shaken for up to 48 hours at ambient temperature. The paper supports were pre-conditioned using THF. The highly viscous casting solution was spread using a doctor blade with a 200 μm gap size. After a certain evaporation time, the evenly coated paper was transferred into a precipitation bath containing deionized water. After 10 minutes in the precipitation bath, the membranes were first dried at ambient conditions and then under reduced pressure at elevated temperatures.

Vapor Phase Functionalization with (3-Aminopropyl)triethoxysilane (APTES) and (3,3,3-Trifluoropropyl) dimethyl chlorosilane (TFPCS).

2 mL of APTES or TFPCS was placed in an evaporating dish inside a desiccator. The membrane was positioned face up directly above the liquid APTES, and the desiccator was gradually evacuated to 0.02 mbar or 0.15 mbar to promote vapor-phase reactions of APTES and TFPCS, respectively. After 72 h under these conditions, the functionalized membrane was removed from the desiccator and allowed to dry at room temperature.



Material Characterization

Standard size exclusion chromatography (SEC) was performed with a 1260 Infinity II (Agilent Technologies) system. In this study, THF was used as the mobile phase (HPLC grade, flow rate 1 mL min⁻¹) on an SDV column set from Polymer Standard Service (PSS) (SDV 10³ Å, SDV 10⁵ Å, SDV 10⁶ Å, 5 µm) with a PSS SECurity2 RI/UV detector. Calibration was carried out using polystyrene (PS) standards from PSS. PSS WinGPC® UniChrom V 8.31 was used for data acquisition and measurement evaluation.

With dimethylformamide (DMF) as the mobile phase (flow rate 1 mL min⁻¹, containing 1 g L⁻¹ LiBr) a PSS GRAM Analytical column set from PSS (30 Å, 10³ Å, 10³ Å) is used at a temperature of 50 °C. The Calibration for this set-up is based on poly(methyl methacrylate) (PMMA) standards from PSS.

Fourier-transform infrared spectroscopy (FTIR) spectra were recorded on an attenuated total reflection Fourier transform infrared (ATR-FTIR, diamond ATR) instrument (Bruker Alpha II) in the 400-4000 cm⁻¹ range with a resolution of 4 cm⁻¹.

Scanning electron microscopy (SEM) was performed on a ZEISS GEMINI 500 microscope using SmartSEM Version 6.07. The samples were mounted on an aluminum stud using adhesive copper tape and sputter-coated with approximately 6 nm platinum using an Automatic Turbo Coater PLASMATOOL 125 SIN 2020_131 from Ingenieurbüro Peter Liebscher.

Static water contact angle (WCA) measurements were performed using a Hamilton syringe (100 µL), a syringe pump (KD Scientific, adjusted to 10 µL), and a custom-made xyz-positioning table. In standard measurements, deionized water was used. Photographs were collected using a Nikon D54000 and digiCamControl 2.1.2.0, OpenDrop 3.3.1⁶⁵ was used for evaluation. The WCA was measured from three



different spots on the sample. The absorption time is the total duration from the initial contact of the water droplet until it visibly disappears. Data are presented as mean $\pm$ standard deviation (SD).

Nuclear magnetic resonance (NMR) spectra for the characterization of the different polymers in solution were recorded on a Bruker Avance II 400 spectrometer with a 9.4 T Ultrashield Plus Magnet and a BBFO probe, and were referenced to the solvent signals.⁶⁶ For processing and evaluation of the spectra, MestReNova 14.2.0 was used.

DNP-enhanced solid-state NMR experiments were performed on samples prepared according to the literature.^{63, 67} Typically, 10 mg of each material is mixed with ca. 10 μ L of a 15 mM AMUPol D₂O/H₂O (9:1) (AMU) or a 15 mM TEKPol in TCE (TEK) solution. Samples were packed into 3.2 mm sapphire rotors and sealed with a Teflon plug and a ZrO₂ driving cap.

All DNP-enhanced solid-state NMR spectra were recorded on a Bruker Avance III 400 MHz DNP spectrometer operating at 9.4 T according to frequencies of 401.63 MHz, 100.99 MHz, and 79.79 MHz for ¹H, ¹³C, and ²⁹Si, respectively. This spectrometer is equipped with a 9.7 T Bruker gyrotron system generating microwaves with a frequency of 263 GHz. The spectra were measured at nominally 120 K with a 3.2 mm low temperature probe operated in 1H/X double mode.

¹H $\rightarrow$ ¹³C CP MAS DNP spectra were recorded at 8 kHz spinning. Spectra were acquired with a contact time of 2 ms. The acquisition time was set to 30 ms, and the excitation pulse length of the 90° Pulse on the ¹H channel was set to 3 μ s. The recycle delay was varied depending on the sample and radical matrix, as summarized in **Table S8** and **Table S9**. Each spectrum was recorded, accumulating 512 scans. Heteronuclear decoupling was performed during data acquisition employing the tppm15 decoupling



sequence.⁶⁸ Referencing was done with respect to TMS (0 ppm) according to literature,⁶⁹ employing kaolinite (−92.5 ppm) as the external standard for ²⁹Si.⁶⁸

¹H→²⁹Si CP MAS DNP spectra were recorded at 8 kHz spinning. The spectra were acquired with a contact time of 0.5 ms. The acquisition time was set to 25 ms and the excitation pulse length of the 90° Pulse on ¹H channel to 3 μs. The recycle delay was varied depending on the sample and radical matrix, as summarized in **Table S8** and **Table S9**. Each spectrum was recorded, accumulating 5120 scans. Heteronuclear decoupling was performed during data acquisition employing the tppm15 decoupling sequence.⁶⁸ The ¹³C dimension was referenced to tetramethylsilane (TMS) employing adamantane (−38.5 ppm) as an external standard.

Permeance Measurements were carried out using a measuring cell as a dead-end setup with a total volume of 400 mL. For all measurements, an external pressure of 0.2 bar was applied using N₂. Membranes were measured over a time of up to three hours in intervals of approximately 10 to 11 min. For all measurements, circular samples with a diameter of 10 mm were used. All samples were preconditioned by immersing them for 30 min in deionized water (MilliQ).

RESULTS AND DISCUSSION

Synthesis of the Linear and Star-shaped Block Copolymer

The linear amphiphilic AB BCP was synthesized in a sequential approach via living anionic polymerization. (**Scheme 1a**) First, the more hydrophobic block segment was prepared from styrene using *s*-BuLi as the initiator. The living chain ends were modified using DPE to ensure the polymerization of the following methacrylate-based monomer.^{51, 52, 70, 71} SMA was used to incorporate a more hydrophilic second block segment. The living chain ends were quenched after the second polymerization step using



MeOH as a proton source. A corresponding ^1H -NMR spectrum of the BCP is displayed in **Figure 1a**. Characteristic signals were observed for each block, as assigned in the spectrum. To reveal the amphiphilic character of the BCP, the polymer was treated with HCl in an aqueous environment to cleave off acetone as the protecting group, thereby yielding two hydroxy moieties and converting the PSMA block into a poly(2,3-dihydroxypropyl methacrylate (PDHPMA) block segment. The corresponding ^1H -NMR spectrum for PS-*b*-PDHPMA is shown in **Figure 1c**. The SEC measurements for each synthesis step are displayed in **Figure 2**. **Figure 2a** shows the linear BCP with the more hydrophobic block segment (blue) and the BCP (red), and after deprotection in **Figure 2b**. As expected for this polymerization technique, the BCP shows a narrow molar mass distribution, confirming good control over the polymerization. Compared to the SEC trace for its first block (Figure 2a), made from styrene, no broadening of the molecular weight distribution was observed. Only an increase in molecular weight was observed. The dispersity of $D = 1.07$ (**Table 1**) indicated a good control over the polymerization without noticeable termination reactions during initiation of the second monomer. For the deprotected PDHPMA, a small increase in molecular weight is observed (Figure 2b) compared to the protected PSMA form (Figure 2a), likely due to interactions between the PDHPMA hydroxy moieties. The polymer also showed an increased dispersity.⁵² For the preparation of the star-shaped $(\text{AB})_n$ BCP and for gaining access to additional morphologies,^{72, 73} another suitable synthesis pathway was used (**Scheme 1b**). The star-shaped BCP was prepared in a convergent arm-first approach using living anionic polymerization. First, to enable an architecture in which the more hydrophilic block is on the outside of the star structure, the more hydrophilic block (based on SMA) was polymerized first using DPHLi. This time, MMA was used for the second, more hydrophobic block of the BCP because of its greater reactivity in living anionic polymerization than styrene. To branch the linear BCPs and thus generate star-shaped $(\text{AB})_n$ BCPs, 1,4-butanediol dimethacrylate (BDDMA) was added in a third step and stirred for several hours. To unveil




the hydroxy moieties, the received polymerization product was treated in a manner similar to that of the linear PS-*b*-PSMA (Scheme 1a). A ^1H NMR spectrum is presented in **Figure 1b**, revealing characteristic signals for both PMMA and PSMA. For BDDMA, no characteristic signals are observed due to its low number of repeating units. SEC traces of the $(\text{PSMA-}b\text{-PMMA})_n$ are shown in **Figure 2c**. **Figure 1d** shows an NMR spectrum for its deprotected form PDHPMA-*b*-PMMA measured in pyridine- d_5 , again displaying three signals at 4.63 ppm, 4.51 ppm, and 4.11 ppm as assigned to the side chain of PDHPMA. In the SEC measurement for the crosslinking product, a bimodal distribution is observable. (**Figure 2d**) This distribution indicated a mixture of two types of star-shaped BCPs. An assumption based on the trace maxima is presented in **Figure S1**. It indicates a combination of a linear ABBA BCP and a four-arm BCP by comparison of the molecular weight of both maxima and the molecular weight of the linear precursor listed in Table 1. The SEC measurement of PSMA-*b*-PMMA unveils two more species at lower molecular weights (Figure 2c). These species can be connected to unreacted PSMA and unreacted PSMA-*b*-PMMA. Similar to a linear BCP, the molar fraction of the second block (Table 1) is calculated from the ^1H -NMR spectrum of the PSMA-*b*-PMMA displayed in Figure 1c, following **Eq S1**. Like the linear PS-*b*-PDHPMA, the molecular weight distribution of the star-shaped PMMA-*b*-PDHPMA has a broader molar mass distribution (Figure 2d), featuring a dispersity of $\bar{D} = 1.52$ compared to $\bar{D}_{\text{Star BCP}} = 1.13$. A significant increase in the apparent molecular weight was also observed. For a better comparison the linear BCP as well as the star-shaped BCP were protected using benzoic anhydride in pyridine to protect the hydroxy moieties of the PDHPMA block.⁵² Both BCPs were then analyzed in SEC using THF as well as DMF as a solvent. The results are given in **Figure S2** as well as in **Table S1**. Each Bz-protected species appears with a slightly increased molecular weight compared to the PSMA-species in THF. The received molecular weights for the Bz-protected species in both samples in DMF are lower than those in THF. This could be given due to different setups for both solvents. Since both samples follow the same trend for the



Bz-protected species, the contradictory observations could be based on the interactions between hydroxy moieties of the more hydrophilic block. Furthermore, the isolation of the star-shaped BCP via inverse precipitation was not successful. Because of this, the polymer was used further as a blend for the membrane preparation.



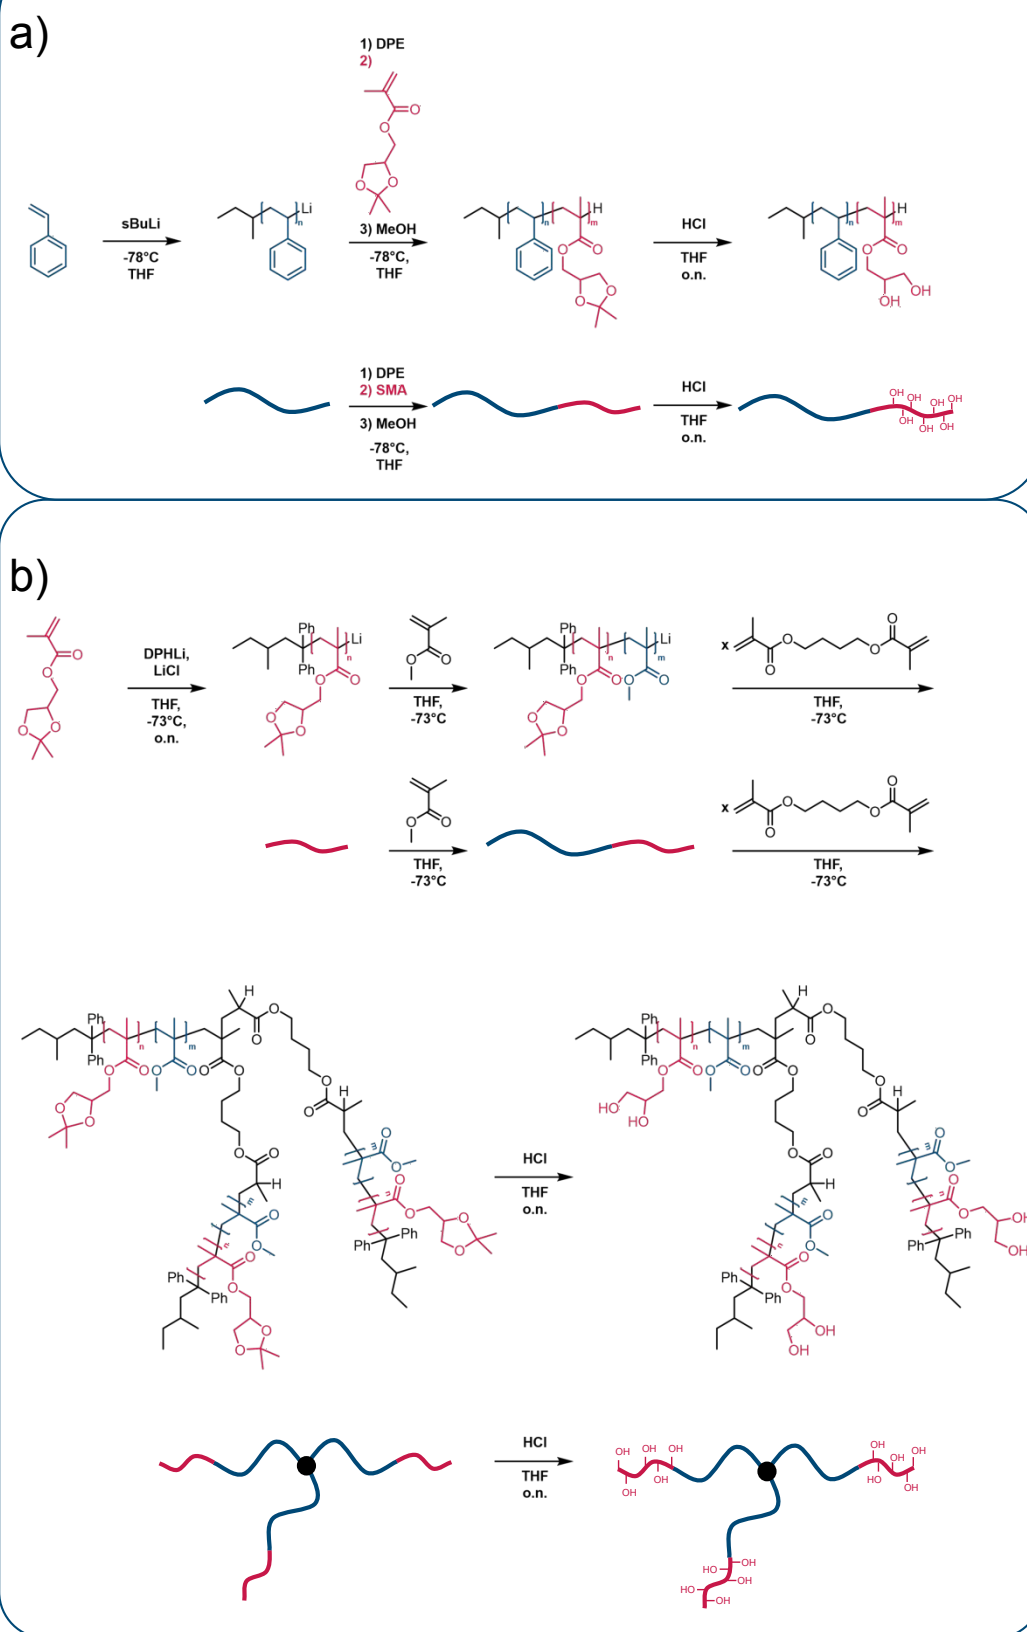

Scheme 1: Synthesis route for the linear BCP (a) and one possible star-shaped BCP (b), including the deprotection step of PSMA (red) to unveil the more hydrophilic PDHPMA block (red).



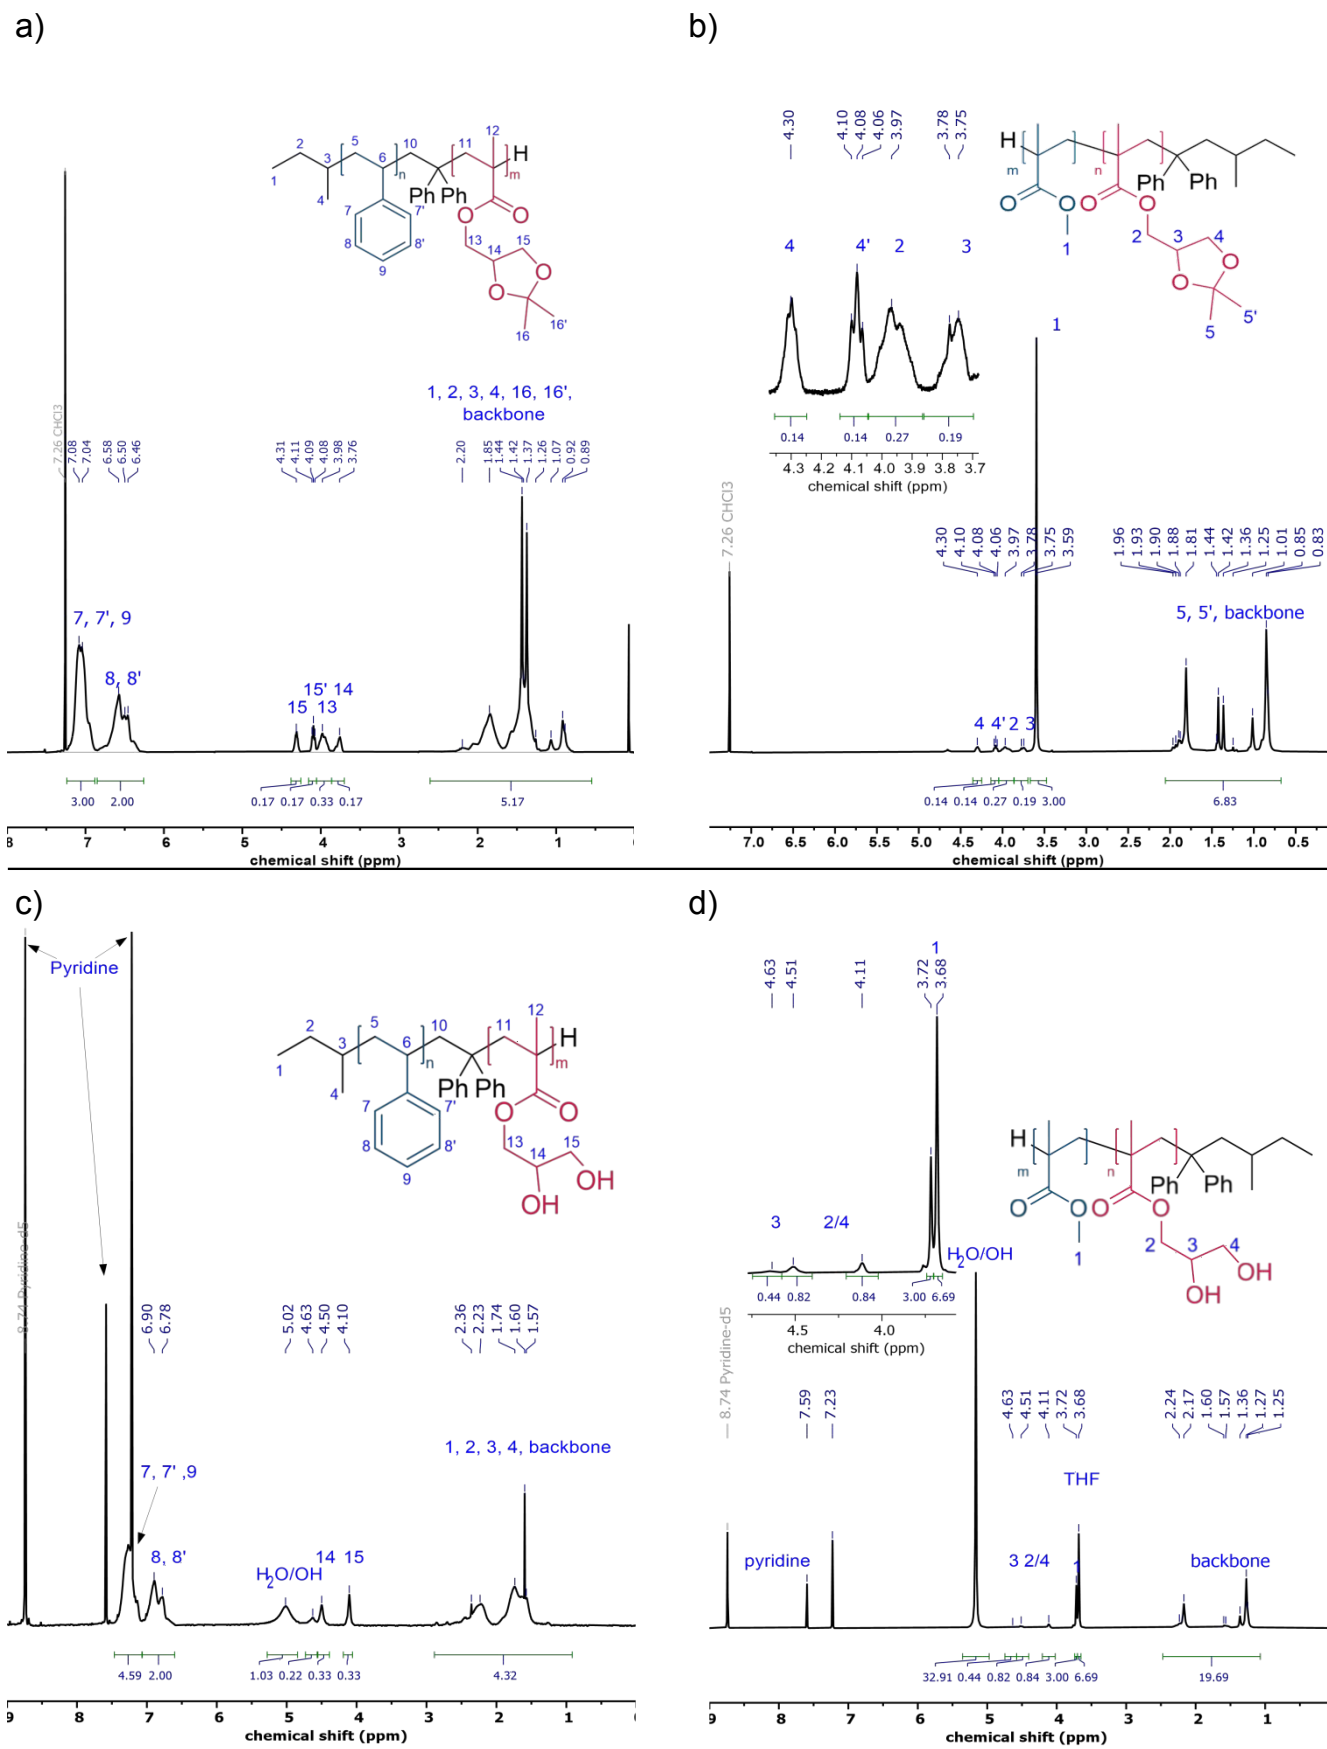


Figure 1: ^1H -NMR spectra of the linear BCP before (a) and after deprotection (c), as well as the star-shaped BCP before (b) and after deprotection (d), with the assigned hydrogens in blue. The NMR spectra of the protected form were measured in CDCl_3 . For the deprotected polymer, pyridine- d_5 was used as a solvent.

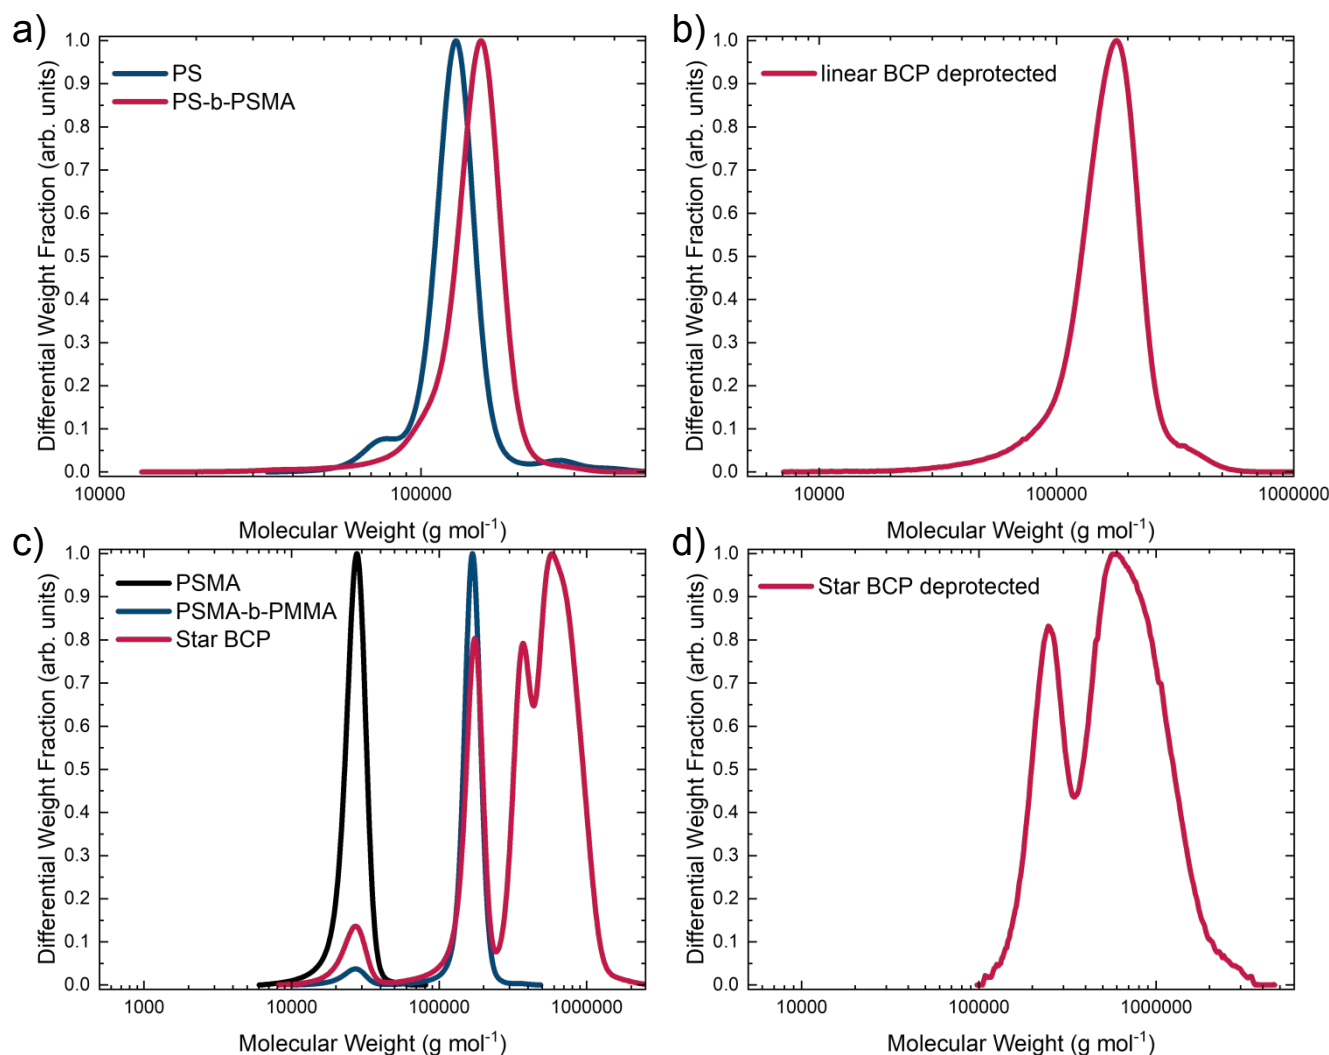


Figure 2: Compilation of SEC measurements for each step in polymer synthesis for the linear BCP (a) in THF with PS calibration, and deprotected (b) in DMF vs. PMMA calibration. The star-shaped BCP in THF vs. PS calibration is shown in (c) with its deprotected form in DMF vs. PMMA calibration (d).



Table 1: Compiled analytical data for both BCP architectures displaying apparent M_n for each segment and related dispersity $\mathcal{D}$ given in brackets:

	M_n [g mol ⁻¹] ($\mathcal{D}$)					$X_{\text{hydrophilic}}^b$
	Hydrophobic block	PSMA block	AB BCP	(AB) _n BCP	deprotected ^c	
Linear BCP	122,000 ^a (1.07)	33,600 ^b	138,200 ^a (1.07)	-	143,740 (1.19)	0.14
Star BCP	90,700 ^b	25,400 ^a (1.05)	163,500 ^a (1.03)	538,000 ^a (1.13)	439,830 (1.52)	0.12

^aSEC measurement in THF against PS calibration, ^bcalculated from NMR before deprotection, ^cSEC measurement in DMF against PMMA calibration

Membrane Preparation and Post-Modification

For membrane preparation, substrates consisting of neat cellulose fibers were used to maximize the effect of the polar BCP segment on the cellulose fiber surface. These cellulose sheets originate from cotton Linters fibers and are therefore referred to as Linters paper in the following. The membranes were prepared according to a SNIPS protocol, and different batches were prepared. To estimate the evaporation time, a crucial parameter for the pore-formation process, a first batch comprising three membranes, **M1a** – **M1c** (Figure S3), was prepared. The composition of the highly viscous polymer solution is listed in Table S2. For all batches, a solvent mixture containing THF, DMF, and DOX in the weight ratio of 2:1:1 was used. Additionally, CuCl₂ was used as an additive to increase the solution viscosity and thus enhance pore order.^{52, 74} THF was used for the major, more hydrophobic block, while DMF was used for the minor, more hydrophilic segment.⁵² DOX was used for the modification of the solvent blend and thus enhanced pore formation⁷⁵. Each membrane of the first batch differs in evaporation time: 10, 22, and 16 seconds. (Table S3) Other conditions to be considered are listed in detail there. Based on the surface structure and the uniformity of the porous structure, an evaporation time of 16 seconds was chosen for further membrane fabrication. As presented exemplarily in Figure S4, **M1a** (left) exhibited a sponge-like



substructure beneath the selective layer. For **M1c**, a surface defect is displayed in Figure S4 (right). This surface defect unveils a porous substructure for this sample as well. To supply larger membranes for the subsequent post-modification step, a second batch was produced under the same conditions. By maintaining the relative humidity and temperature during membrane preparation for the second batch (Table S4), as in the first batch, the membranes exhibited average pore sizes of 49.9 ± 14.9 nm for **M2a** and 42.3 ± 9.9 nm for **M2b**. A compilation for both membranes is given in Table S5. Both membranes are presented in Figure 3a and 3c. Close-ups of both samples are also presented in Figures 3b and 3d. These images were also used to determine the average pore diameter. An example of such a measurement is shown in Figure S5, where each diameter taken was highlighted in yellow. Furthermore, a histogram for each pore diameter determination is given in Figure S6. Compared to the first batch, the pores appear approximately 13 nm larger for **M2a** (Table 2, Table S3). As displayed in Figure 2a and Figure 3a, the surface of **M2a** appeared more ruptured and thus less uniform in pore structure. This could result in a larger average pore diameter, which is consistent with the larger standard deviation for **M2a** shown in Table 2. **M2b** (Figures 3b), on the other hand, exhibited a surface structure like that of **M1c** presented in Figure S3. The pore-size distribution for **M2b** was similar to that of **M1c**. Only the pores are about 7.5 nm larger in diameter. For the membrane (**M3**, Table S6 and Table S7), originating from a star-shaped BCP, porous structures were obtained (Figure 3c and d), with an average pore diameter of 35.2 ± 6.2 nm (Table 2). The pores appear smaller than those in the second batch based on the linear BCP, while maintaining a similar block distribution. For investigations of branched BCPs in the bulk state, observations were made where certain domains appeared narrower compared to microphase separations of similar BCPs in a linear configuration.⁷³ Based on the behavior in the bulk state, branched systems such as these star-shaped BCPs could thus lead to a smaller pore diameter on average in such porous materials. Similar behavior was also observed of blend systems of linear block copolymers.⁷⁶



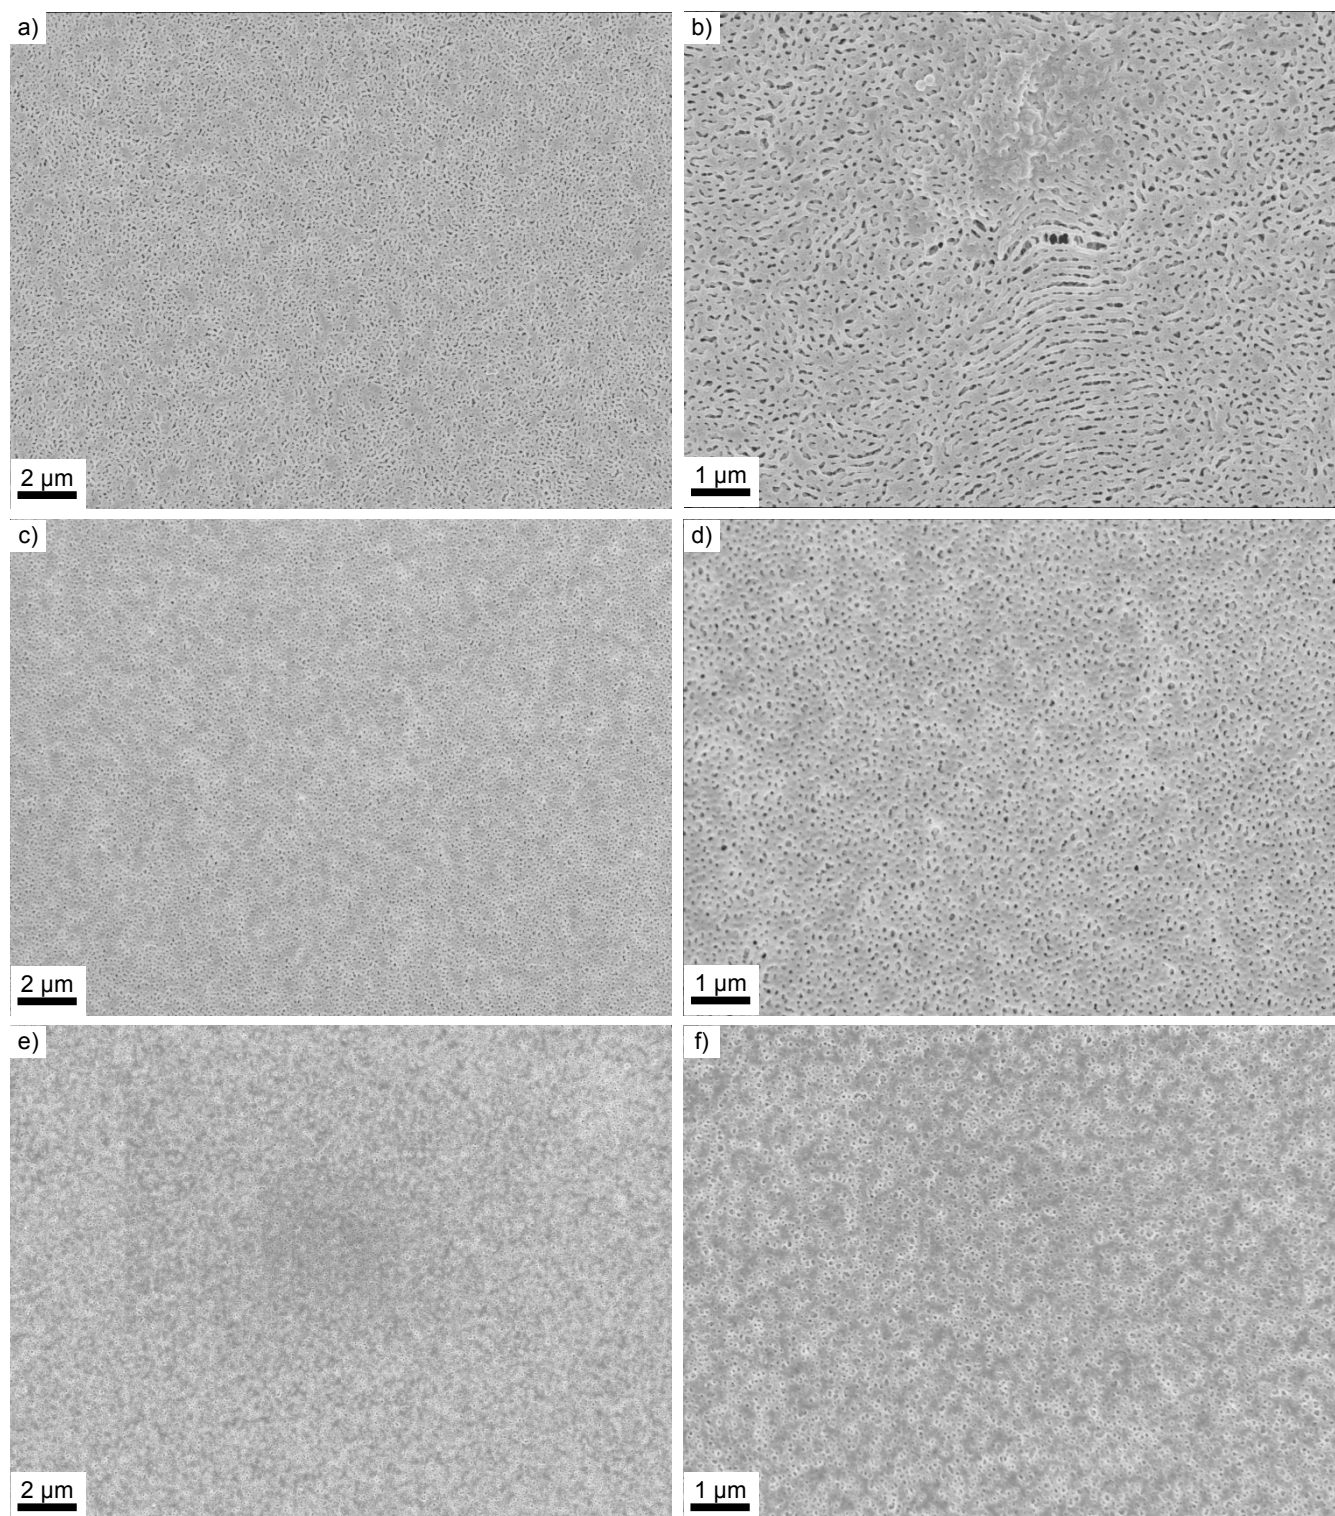


Figure 3: The prepared membrane M2a is shown as an overview (a) and with magnification (b). Membrane M2b is displayed in an overview (c) and at magnification (d). The received membrane M3 is displayed as an overview image (d) and with magnification (e).




Table 2: Pore diameters for each membrane measured from 100 defined pores each in random orientations:

Membrane	Type of Polymer used	Modification	Pore size (nm)
M2a	Linear BCP	Pristine	49.9 ± 14.9
		APTES	37.6 ± 9.4
M2b	Linear BCP	Pristine	42.3 ± 9.9
		TFPCS	38.4 ± 9.6
M3	Star-shaped BCP	Pristine	35.2 ± 6.2
		APTES	26.7 ± 6.3
		TFPCS	-

Qualitative Characterization of Modified Porous Structures using FTIR and Solid-State NMR Spectroscopy

The Linters cellulose-based hybrid membranes were further modified with TFPCS or APTES to tune the porous material's surface properties, as shown in **Scheme 2**, with APTES in orange and TFPCS in yellow. In this section, molecular analyses following the post-modification protocols were performed to confirm the successful vapour-phase reaction steps and cellulose modification. By using the surface-exposed hydroxy moieties derived from the PDHPMA block of the BCP (red), new functional groups can be introduced via substitution reactions at silicon units bearing functional groups. The post-modification of the membranes was carried out using a vapor phase modification method.⁷⁷



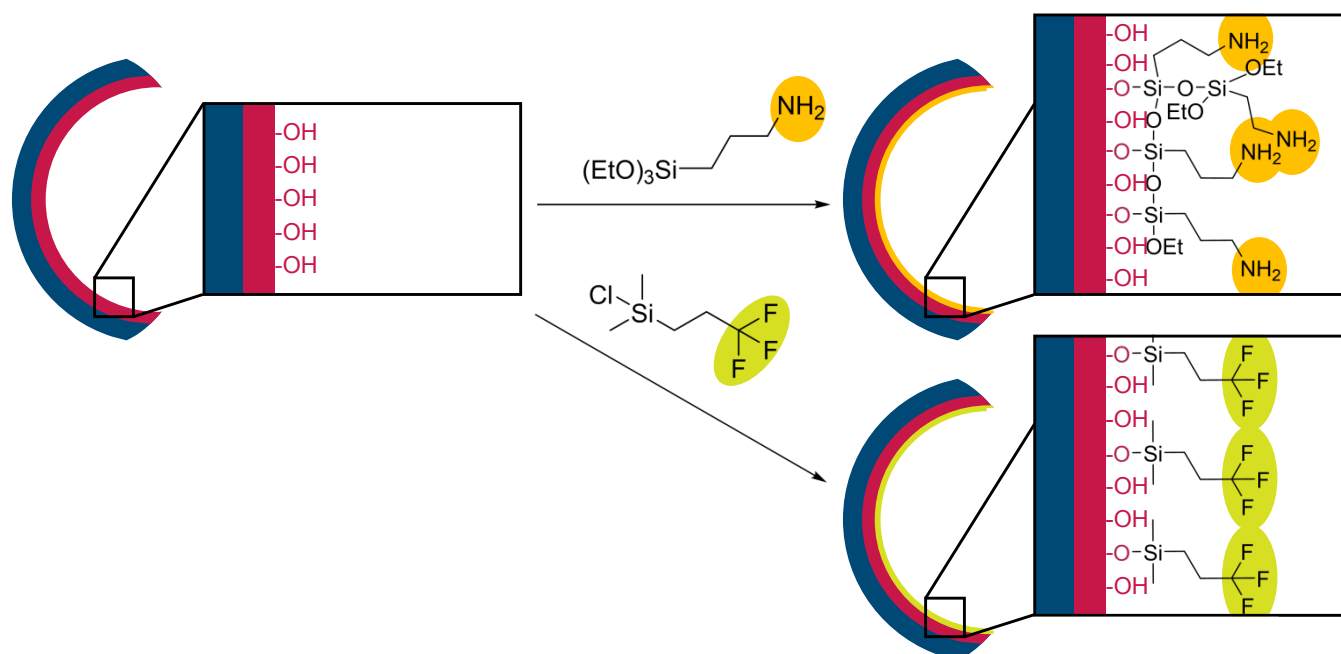

Scheme 2: Process of post-modification of a pore for APTES with possible multilayer formation (top) and TFPCS as a monolayer (bottom).

The characterization of the membranes **M2a** and **M2b** was done by FTIR spectroscopy, as shown in **Figure 4**. For reference, the spectrum of a pristine membrane sample is displayed in black (**Figure 4, top**), an APTES-modified membrane is shown in blue (**Figure 4, middle**), and a membrane after TFPCS is presented in red (**Figure 4, bottom**). The pristine membrane spectrum displayed characteristic absorption bands of the coated linear BCP, including a broad OH stretching band at 3600-3100 cm^{-1} , C-H aromatic stretching at 3080-3027 cm^{-1} , C-H aliphatic stretching at 2924-2850 cm^{-1} , C=O stretching at 1724 cm^{-1} , aromatic ring C=C stretching or ring vibrations at 1603-1452 cm^{-1} , and C-O stretching at 1158 cm^{-1} . After modification, the APTES-modified spectrum showed a clear band at 1550 cm^{-1} , indicating N-H bending, and an increased intensity in the Si-O-Si/Si-O-C stretching region between 1000-1100 cm^{-1} , confirming the presence of amine and siloxane groups from APTES.⁷⁸ Similarly, the TFPCS-modified spectrum revealed the appearance of specific peaks, including C-F stretching of the CF₃ group at 1263 cm^{-1} and Si-C stretching at 842 cm^{-1} , providing strong evidence for the covalent attachment of the fluorinated silane



(TFPCS).⁷⁹ Both modifications in the gas phase appear to affect the membrane structure, with the pore size decreasing during the modifications. Surfaces and pore diameters are compiled in Figure 4 and Table 2. For the appearance of M2a before modification (**Figure 5a**) and after modification (**Figure 5b**), at higher magnification, a surface structure was observable. Changes to the TFPCS approach can also be concluded from **Figure 5c** and **Figure 5d**. The change in surface structure resulted in a smaller pore size for both membranes, as listed in Table 2. For APTES modification, a decrease in pore diameter of approximately 12 nm was monitored. For the TFPCS modification, a decrease of approximately 4 nm was observed. It could be correlated with the type of anchoring unit. A trifunctional anchoring unit can lead to a multilayer coating and, consequently, a thicker layer, as indicated in Scheme 2. For M3, the post-modification was performed using the same protocol as for M2a and M2b. For the sample M3, post-modification with APTES resulted in a decrease in pore diameter of approximately 9 nm, while retaining the surface appearance (**Figure 5e** and **5f**). This matches the observations made before. Surprisingly, for the sample reacted with TFPCS, the porous structure vanished completely, as shown in **Figure 5g**. APTES with its three ethoxy-moieties is able to generate a multi-layer structure at the pore surface. Such a multi-layer could be capable of stabilizing the structure during the post-modification process.^{62, 80} In contrast, the anchoring unit, which is used in TFPCS, is only capable of building up a monolayer. Based on that, a loss of structure on the surface could be connected to the ability of the post-modification reagent to build stabilizing multi-layer structures.



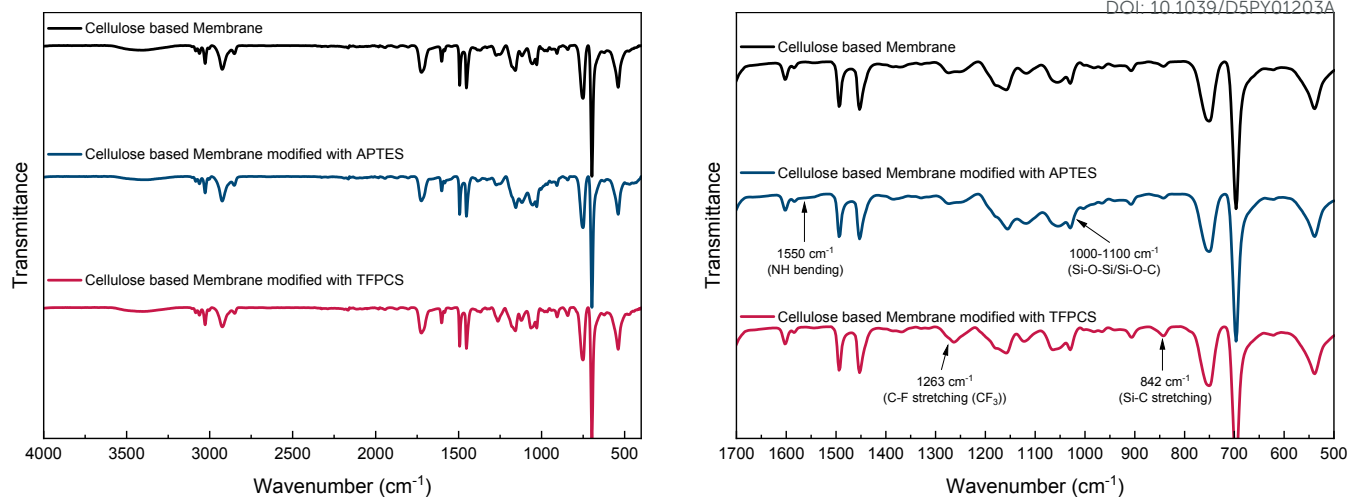


Figure 4:-FTIR spectra of the cellulose-based membrane coated with a porous structure based on PS-b-PDHPMA before post-modification (black), after ATPES modification (blue), and TFPCS modification (red). On the left side, an overview is given, while on the right, a detailed presentation is given.



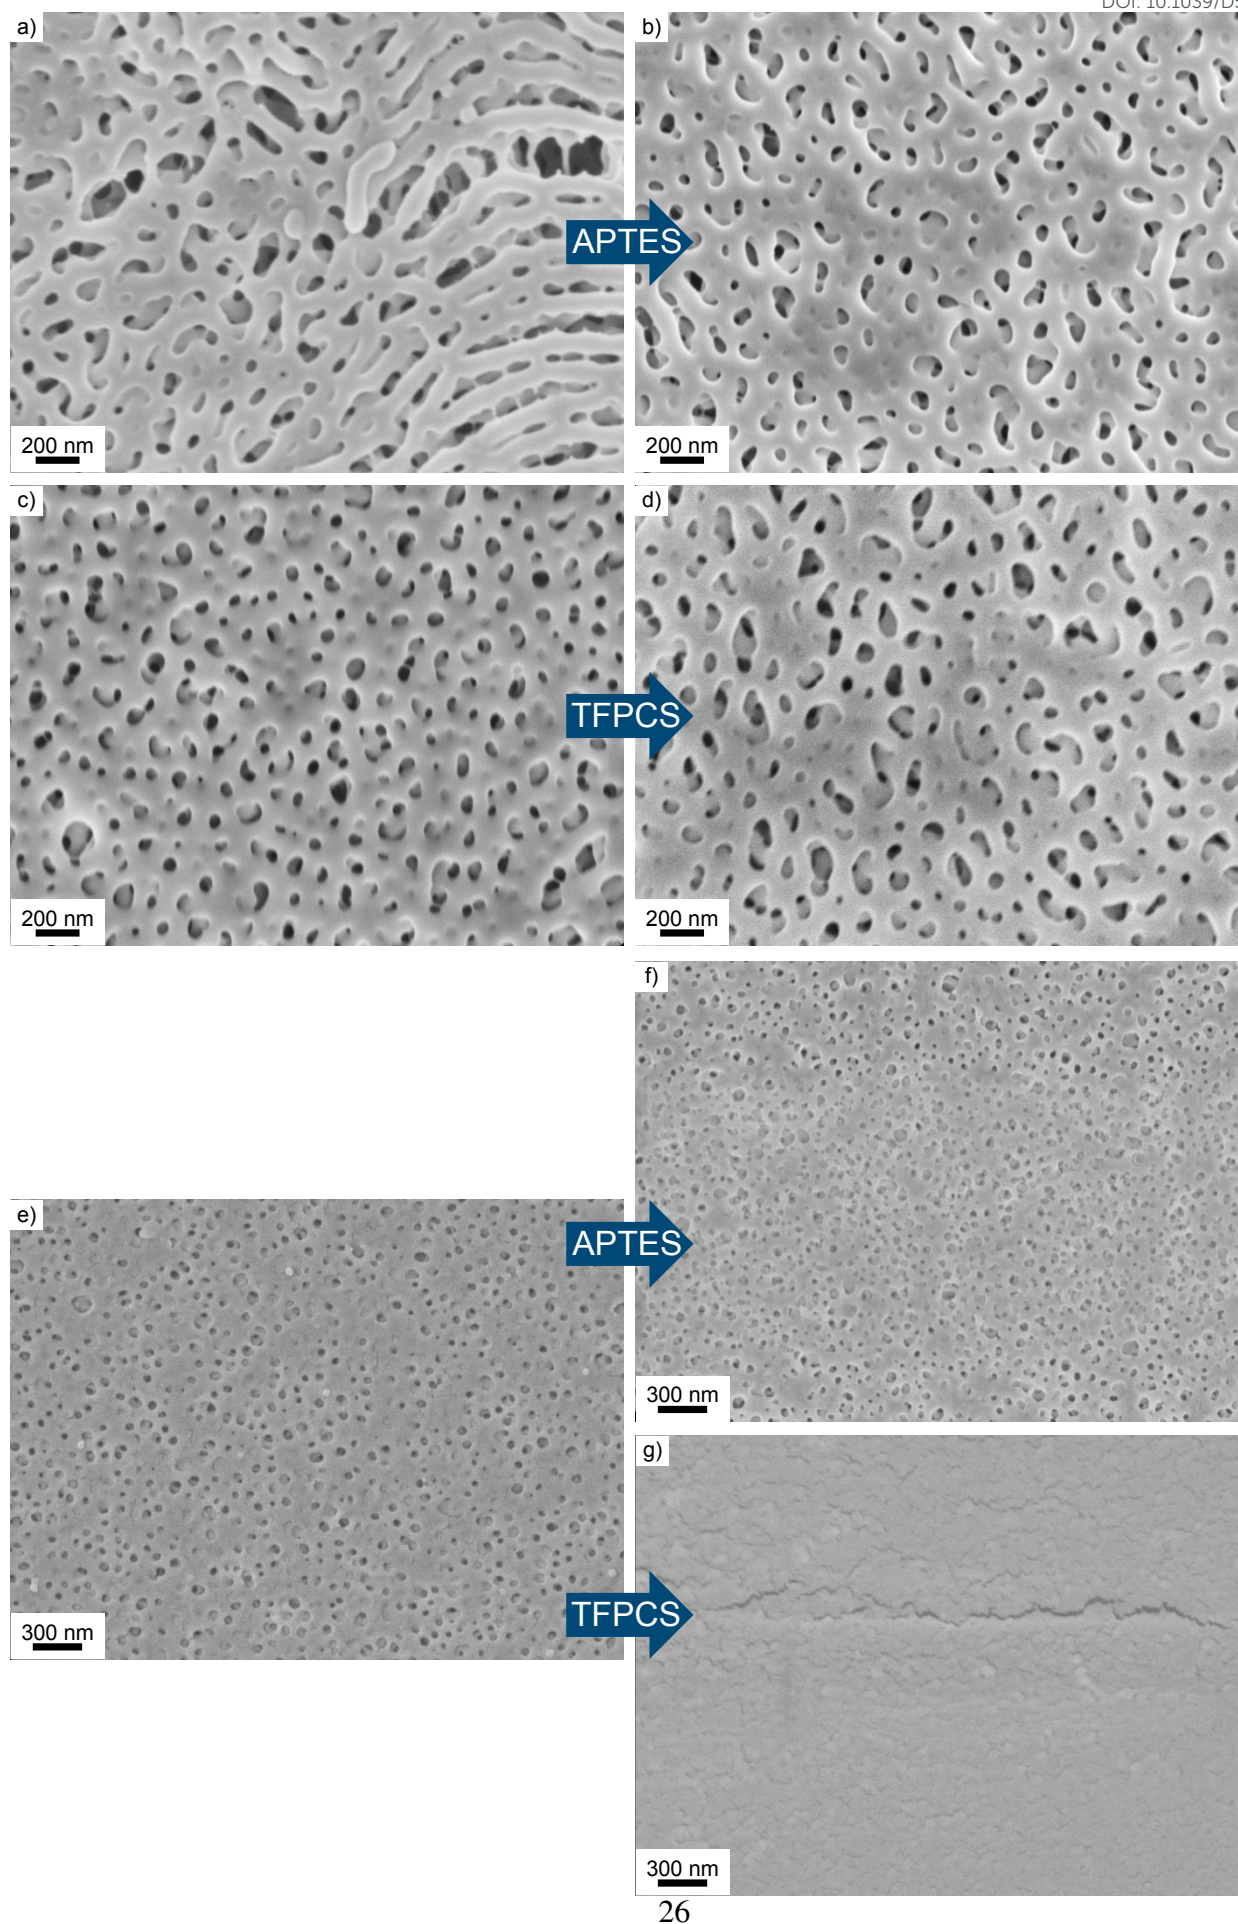


Figure 5: Membranes based on the linear BCP are shown before post-modification (a) and after post-modification with APTES (b) and TFPCS (c). Membranes based on star-shaped BCPs (M3) before post-modification (e) and after post-modification with APTES (f) and TFPCS (g).

Comparison of the FTIR spectra confirmed the successful surface modification of PS-*b*-PDHPMA membranes at Linters paper. By varying functional groups, e.g., fluorinated functional groups in the case of TFPCS or amines for APTES, surface properties like polarity can be tuned. The consequences of both surface modifications are discussed in the following in the context of water contact angle measurements and water permeance.

To analyze the detailed structure of the distorted, highly complex membrane and modified membrane systems, as a complementary analytical approach, selectively enhanced DNP solid-state NMR was applied. With this technique, it is feasible to easily distinguish between structure moieties in more hydrophobic or more hydrophilic environments. When comparing the DNP-enhanced $^1\text{H} \rightarrow ^{13}\text{C}$ CP MAS spectra (**Figure 6a**) of the Linters paper, modified with PS-*b*-PDHPMA (M2) prepared with TEK as radical-solvent system, no pronounced differences were observed among the three membranes. This indicates that the environments of the carbon nuclei of the cellulose and polymer matrix remain essentially unchanged after surface modification. In contrast, the DNP-enhanced $^1\text{H} \rightarrow ^{13}\text{C}$ CP MAS spectra of the Linters paper modified with PMMA-*b*-PDHPMA (M3) (**Figure 6b**) show noticeable changes only for the TFPCS-modified membrane. The characteristic peaks of the TFPCS moiety appear at 2, 10, and 29 ppm, whereas no new signals are observed for the APTES-modified membrane. To confirm that the newly observed peaks indeed originate from the TFPCS functionality, the spectrum was compared with that of TFPCS-modified SBA-15 (**Figure 6c**). The identical peak positions in both materials strongly indicate the successful incorporation of TFPCS on the membrane surface. Then, DNP-enhanced $^1\text{H} \rightarrow ^{29}\text{Si}$ CP MAS



spectra (**Figure 6d**) were analyzed to probe silicon-containing functional groups introduced during the modification and to distinguish between APTES- and TFPCS-functionalized surfaces clearly. The DNP-enhanced $^1\text{H} \rightarrow ^{29}\text{Si}$ CP MAS spectrum of the APTES-modified membrane shows a broad asymmetric signal at -68 ppm, which is assigned to T_n groups [$\text{CH}_3(\text{OSi})_3$] originating from the covalent attachment of the APTES linker to the membrane surface. In contrast, the TFPCS-modified membrane shows a signal around +7 ppm, corresponding to M groups [$(\text{CH}_3)_3\text{Si}$], indicative of trimethylsilyl groups. The presence of these distinct signals clearly underlines the successful surface modification by APTES and TFPCS, respectively. The TFPCS-modified M3 membrane displays a significantly more intense M-group signal compared to the TFPCS-modified M2 membrane, suggesting that TFPCS couples more effectively or in higher amounts to the M3 membrane. In contrast, the APTES-modified membranes show comparable T_n signal intensities for both M2 and M3, indicating that the extent of APTES functionalization is similar across both membrane systems.



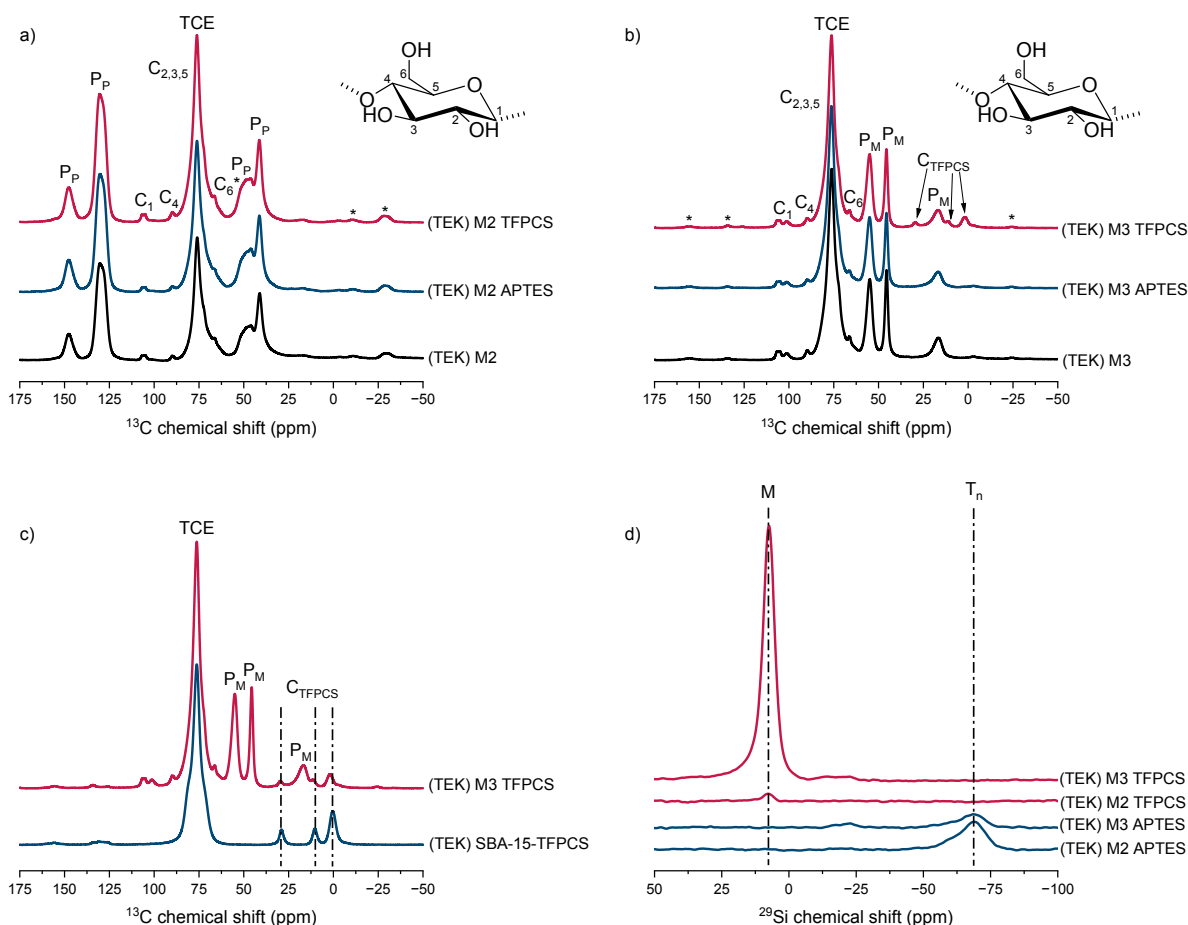


Figure 6: (a) DNP-enhanced $^1\text{H} \rightarrow ^{13}\text{C}$ CP MAS spectra of the unmodified membrane (Linters paper + PS-*b*-PDHPMA membrane (M2)), the APTES-, and the TFPCS-modified membranes measured. (b) DNP-enhanced $^1\text{H} \rightarrow ^{13}\text{C}$ CP MAS spectra of the unmodified membrane (Linters Paper + PMMA-*b*-PDHPMA membrane (M3)), the APTES-, and the TFPCS-modified membranes were measured. (c) DNP-enhanced $^1\text{H} \rightarrow ^{13}\text{C}$ CP MAS spectra of the TFPCS-modified SBA-15 and the TFPCS-modified membranes were measured. (d) DNP-enhanced $^1\text{H} \rightarrow ^{29}\text{Si}$ CP MAS spectra of the APTES- and the TFPCS-modified membranes. Note: a 15 mM TEKPol in TCE (TEK) radical-solvent system was used for sample preparations. All spectra were recorded at 8 kHz spinning. Spinning sidebands are marked with an asterisk. Signals referring to the polymer are marked with “P”.

Macroscopic Effects of Surface Modification on Water Contact Angle and Permeance of the Substrate

To further evaluate the influence of post-modification, the materials were studied via WCA in different stages before and after application of APTES or TFPCS. For reference, pure Linters paper as well as Linters paper with APTES-modified and TFPCS-modified surfaces were tested. The results are presented



comparatively in **Table 3** and discussed in the following. During the WCA measurement, the water droplet slowly spread and then disappeared on the porous substrates. Therefore, the static contact angle was measured at 3s after a drop was deposited on the surface, and the absorption time was also measured for comparison. All WCA and absorption times discussed in the following are displayed in Table 3. The WCA and absorption time results clearly show that the unmodified Linters cellulose substrate, which is hydrophilic and porous, exhibited complete and rapid wetting (absorption time < 1 s and WCA = 0). After functionalization of the paper with APTES and TFPCS, the WCA of these modified Linters paper samples was difficult to determine. The water droplet spread out and vanished completely in 12 seconds for APTES-modified Linters paper and in less than 1 s for TFPCS-modified Linters paper. This may be due to the modified cellulose fiber substrate remaining highly porous, since only a thin monolayer of APTES or TFPCS molecules was deposited on the paper surface through vapor deposition. However, APTES-modified paper exhibited a slight increase in wetting resistance, with an absorption time of 12 ± 1 s, compared to unmodified paper. In contrast, the application of the linear BCP resulted in a significant increase in the absorption time (29 ± 10 s). A water contact angle of $25^\circ \pm 2^\circ$ was obtained for the cellulose polymer hybrid M2. After functionalization, both functionalized M2 substrates showed a clear shift toward increased hydrophobicity. The APTES modification caused the most notable change, raising the WCA to $39^\circ \pm 5^\circ$ and significantly increasing absorption time to 106 ± 38 s. Similarly, the TFPCS modification raised the WCA to $35^\circ \pm 5^\circ$ and the absorption time to 48 ± 6 s for M2. This boost in hydrophobicity additionally confirmed that the amine- and fluorinated-silane groups were successfully attached to the M2 membrane surface, consistent with the expected decrease in surface energy.



Table 3: Compilation of Water Contact Angles of different Samples:

Sample	Absorption time [s]	WCA [°]
Linters Paper	<1	0
Linters Paper APTES-modified	12 ± 1	N/A ^a
Linters Paper TFPCS-modified	<1	0
M2b	29 ± 10	25 ± 2
M2 APTES-modified	106 ± 38	39 ± 5
M2 TFPCS-modified	48 ± 6	35 ± 5

^aThe droplet was continuously spreading, making it difficult to obtain an accurate static contact angle.

In the last step, both modified membranes were tested for their water permeance at a slightly increased water pressure of 0.2 bar. The performance was then compared with unmodified **M2a** and **M2b** samples. The development of the permeance for each sample over time is presented in **Figure 7** at the top. On the left, **M2a** is shown without (black) and with APTES modification (blue). The right site represents the development for **M2b** without modification (black) and with TFPCS modification (red). The membrane **M2a** shows a higher overall water permeance than **M2b**. This correlates with the larger pore diameter displayed in Table 2. For both membranes, a strong decrease in permeance is observed for the first 60 to 75 minutes. This was observed earlier as well and can be attributed to swelling of the more hydrophilic block coating the inner pore surface.^{46, 49} After 75 minutes, only a small decrease is observed over up to 125 minutes for **M2a** and 180 minutes for **M2b** with a permeance of approximately 120 L bar⁻¹m⁻² h⁻¹ for **M2a** and 212 L bar⁻¹m⁻² h⁻¹ for **M2b**. For both samples, after modification with APTES or TFPCS, an increase in water permeance is observed for the whole test time. At 82 minutes, the permeance is three times that of the APTES-modified sample with 1885 L bar⁻¹m⁻² h⁻¹. The Permeance for **M2b** is doubled due to TFPCS modification with 454 L bar⁻¹m⁻² h⁻¹. Such observations contrast with the results for the



membranes, particularly for the modified membranes based on the star-shaped BCP **M3**. The overall development of permeance over the entire test period matches the observations from the linear BCP presented earlier. For the pristine sample (Figure 7, black), the permeance is approximately $100 \text{ L bar}^{-1} \text{ m}^{-2} \text{ h}^{-1}$, in a similar order of magnitude to **M2b**. In contrast to **M2a** and **M2b**, no significant influence of the APTES modification for **M3** was observed. While the permeance of the APTES-modified membrane was quite similar, the TFPCS modification reduced the membrane's permeance compared to the pristine **M3** sample. This observation aligns with SEM imaging results and is linked to the loss of pores on the material surface during the post-modification process. Overall, the membranes shown here operate without but also with post-modification in a range of $100 - 1900 \text{ L bar}^{-1} \text{ m}^{-2} \text{ h}^{-1}$, which is typical for amphiphilic SNIPS-like membranes shown in literature before.^{41, 46, 48, 81} With focus on the post-modification of porous structures, the implemented structures during membrane casting could be preserved for APTES-modification. Only during TFPCS-modification of **M3**, a loss of structure was observed.



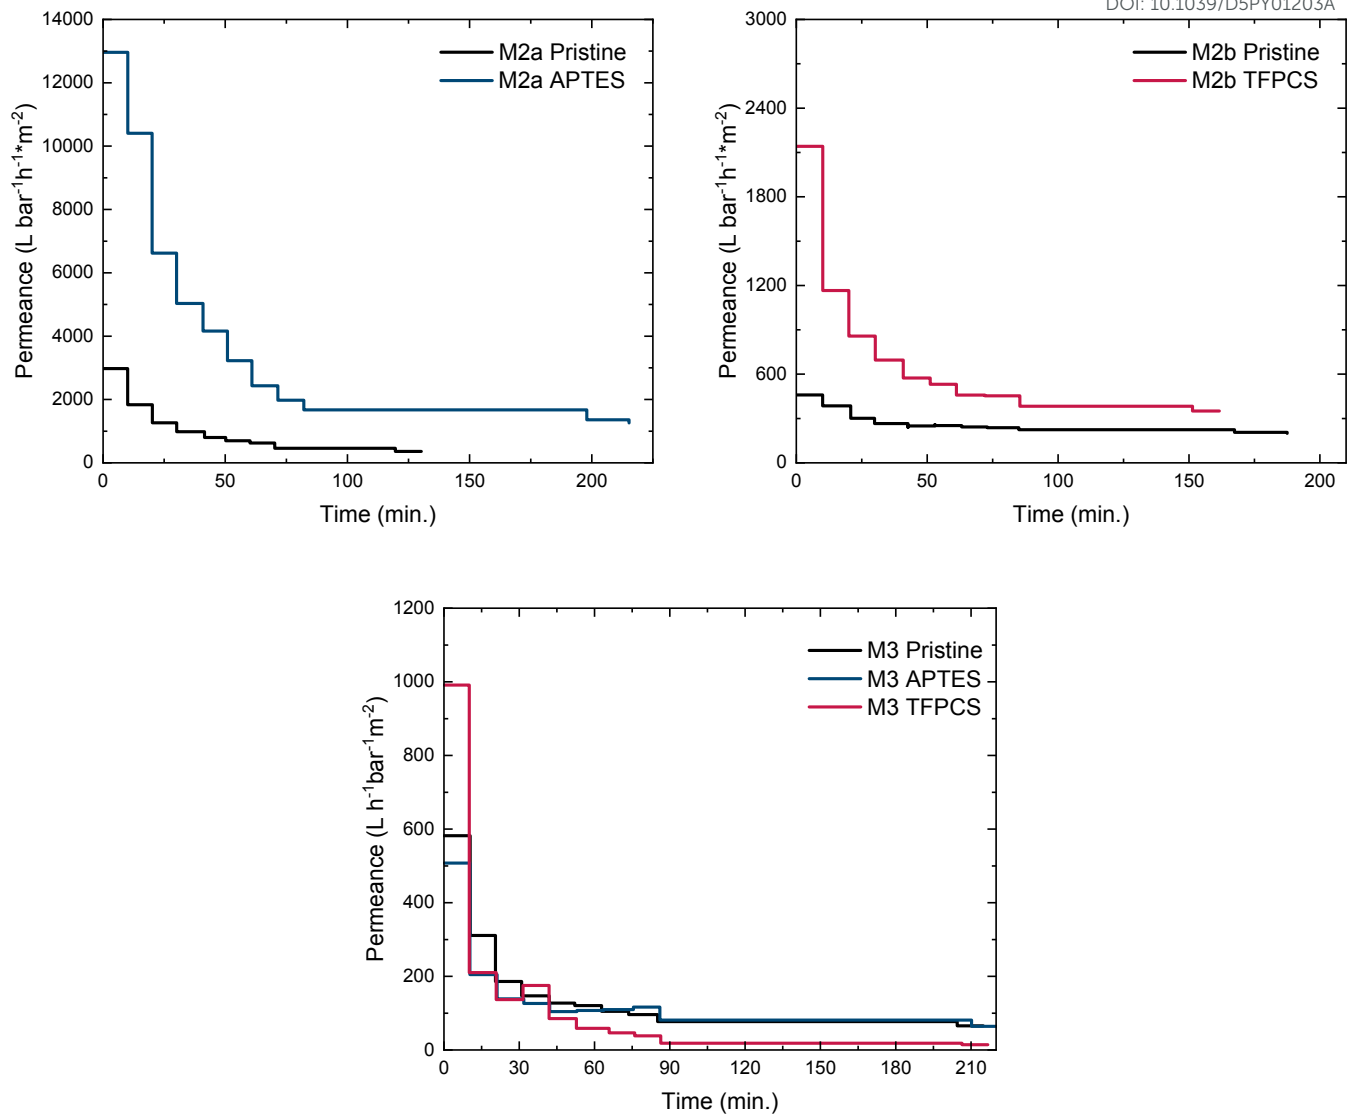


Figure 7: Water permeance measurements of membranes M2a (top left) and M2b (top right) before and after surface modification with APTES (left) and TFPCS (right). A compilation for the M3-based membranes is shown at the bottom.

CONCLUSION

A sequential procedure for the synthesis of an amphiphilic block copolymer based on solketal methacrylate SMA was established by the application of the living anionic polymerization. A defined polystyrene-*block*-polysolketal methacrylate (PS-*b*-PSMA) BCP with a molecular weight of $M_n = 138,200 \text{ g mol}^{-1}$ and a dispersity of $\bar{D} = 1.07$ was achieved and converted into polystyrene-*block*-poly(dihydroxy propyl methacrylate) PS-*b*-PDHPMA by an acid-mediated deprotection step under mild conditions. The protocol was further developed for the preparation of poly(dihydroxy propyl methacrylate)-*block*-polymethyl methacrylate (PDHPMA-*b*-PMMA)_n star-BCP in a convergent arm-first strategy using 1,4-butanediol methacrylate (BDDMA) as a linking unit. Here, a molecular weight $M_n = 538,000 \text{ g mol}^{-1}$ and a dispersity of $\bar{D} = 1.13$ were obtained before conversion of the PSMA block. Both polymers were converted into porous materials in the vicinity of cellulose paper sheets following an SNIPS protocol. For both polymers, porous structures were obtained, while the average pore diameter for the linear BCP tends to appear larger compared to the star-shaped BCP. Pore diameters ranging from 25 to 50 nm were achieved. By using surface-exposed hydroxy moieties, amines, and fluorinated functionalities, the surface properties of the porous materials were manipulated. Using a vapor-phase approach, the surfaces of the resulting porous materials were modified with 3-aminopropyltriethoxysilane (APTES) and 3-aminopropyltriethoxysilane (TFPCS), respectively. SEM imaging indicates a decrease in pore diameter of approximately 5 nm. The influence of the post-modification step was then investigated on a molecular scale using FTIR and DNP-enhanced solid-state NMR, revealing that the TFPCS modification is much more efficient for the PMMA-*b*-PDHPMA membrane (M3) than for the PS-*b*-PDHPMA membrane (M2), whereas APTES modification shows similar efficiency for both membranes. The influence of the post-modification on a macroscopic scale was examined using water contact angle.



Here, for both reagents, a significant increase in contact angle and absorption time was observed. Finally, the porous materials with and without post-modified surfaces were tested as candidates for cellulose-based membrane materials by investigating the development of water permeance over time at slightly elevated pressure. In summary, this work presents promising prospects for producing tailor-made porous cellulose-based materials with precise control over their properties for specific applications.

ASSOCIATED CONTENT

Supporting Information.

AUTHOR INFORMATION

Corresponding Author(s)

*Markus Gallei: markus.gallei@uni-saarland.de

*Torsten Gutmann: gutmann@chemie.tu-darmstadt.de

ORCID

Sebastian Pusse [ORCID 0009-0001-0456-9507]

Waranya Limprasart [ORCID 0009-0005-5524-3741]]

Sebastian Heinz [ORCID 0009-0002-1644-9550]

Samuel Schabel [ORCID 0000-0002-7207-8208]

Volker Presser [ORCID 0000-0003-2181-0590]

Torsten Gutmann [ORCID 0000-0001-6214-2272]



Suteera Witayakran [ORCID 0000-0001-5601-5760]

Markus Gallei [ORCID 0000-0002-3740-5197]

Notes

The authors declare no conflict of interest

ACKNOWLEDGMENT

T.G. gratefully acknowledges the Deutsche Forschungsgemeinschaft (DFG) under grant GU-1650/3–2. W.L. thanks the Development and Promotion of Science and Technology Talents Project (DPST), the Royal Government of Thailand Scholarship, and the Institute for the Promotion of Teaching Science and Technology (IPST) for financial support. This study was performed within the project “Switchable Membrane Systems -SWIMEMSYS”, which is financed by the European Regional Development Fund and the Saarland funds. M.G., S.P., and S.H. would like to thank the European Union and the Ministry of Economics, Innovation, Digitalisation, and Energy for the financial support.



REFERENCES

- (1) Park, H.; Park, B. Review of Microplastic Distribution, Toxicity, Analysis Methods, and Removal Technologies. *Water* **2021**, *13* (19). DOI: ARTN 273610.3390/w13192736.
- (2) Dar, M. A.; Palsania, P.; Satya, S.; Dashora, M.; Bhat, O. A.; Parveen, S.; Patidar, S. K.; Kaushik, G. Microplastic pollution: A global perspective in surface waters, microbial degradation, and corresponding mechanism. *Mar Pollut Bull* **2025**, *210*, 117344. DOI: 10.1016/j.marpolbul.2024.117344 From NLM Medline.
- (3) Nguyen, M. K.; Lin, C.; Nguyen, D. D. Microplastic pollution associated with probabilistic human health risks: Potential hazards, critical factors, challenges, and limitations. *Mar Pollut Bull* **2025**, *221*, 118528. DOI: 10.1016/j.marpolbul.2025.118528 From NLM Medline.
- (4) Ahmadi, P.; Doyle, D.; Mojarad, N.; Taherkhani, S.; Janzadeh, A.; Honardoost, M.; Gholami, M. Effects of Micro- and Nanoplastic Exposure on Macrophages: A Review of Molecular and Cellular Mechanisms. *Toxicol Mech Methods* **2025**, 1-40. DOI: 10.1080/15376516.2025.2500546 From NLM Publisher.
- (5) Gluge, J.; Scheringer, M.; Cousins, I. T.; DeWitt, J. C.; Goldenman, G.; Herzke, D.; Lohmann, R.; Ng, C. A.; Trier, X.; Wang, Z. An overview of the uses of per- and polyfluoroalkyl substances (PFAS). *Environ Sci Process Impacts* **2020**, *22* (12), 2345-2373. DOI: 10.1039/d0em00291g From NLM Medline.
- (6) Bonato, M.; Corra, F.; Bellio, M.; Guidolin, L.; Tallandini, L.; Irato, P.; Santovito, G. PFAS Environmental Pollution and Antioxidant Responses: An Overview of the Impact on Human Field. *Int J Environ Res Public Health* **2020**, *17* (21). DOI: 10.3390/ijerph17218020 From NLM Medline.
- (7) Rekik, H.; Arab, H.; Pichon, L.; El Khakani, M. A.; Drogui, P. Per- and polyfluoroalkyl (PFAS) eternal pollutants: Sources, environmental impacts and treatment processes. *Chemosphere* **2024**, *358*, 142044. DOI: 10.1016/j.chemosphere.2024.142044 From NLM Medline.
- (8) Song, Y.; Phipps, J.; Zhu, C.; Ma, S. Porous Materials for Water Purification. *Angew Chem Int Ed Engl* **2023**, *62* (11), e202216724. DOI: 10.1002/anie.202216724 From NLM PubMed-not-MEDLINE.
- (9) Al-Jubouri, S. M.; Al-Batty, S.; Al-Hamd, R. K. S.; Sims, R.; Hakami, M. W.; Sk, M. H. Sustainable environment through using porous materials: A review on wastewater treatment. *Asia-Pacific Journal of Chemical Engineering* **2023**, *18* (4). DOI: 10.1002/apj.2941.
- (10) Khulbe, K. C.; Matsuura, T. Removal of heavy metals and pollutants by membrane adsorption techniques. *Applied Water Science* **2018**, *8* (1). DOI: 1910.1007/s13201-018-0661-6.
- (11) Regula, C.; Carretier, E.; Wyart, Y.; Gesan-Guizieu, G.; Vincent, A.; Boudot, D.; Moulin, P. Chemical cleaning/disinfection and ageing of organic UF membranes: a review. *Water Res* **2014**, *56*, 325-365. DOI: 10.1016/j.watres.2014.02.050 From NLM Medline.
- (12) Bilyukevich, A. V.; Plisko, T. V.; Lipnizki, F.; Pratsenko, S. A. Correlation between membrane surface properties, polymer nature and fouling in skim milk ultrafiltration. *Colloid Surface A* **2020**, *605*. DOI: ARTN 12538710.1016/j.colsurfa.2020.125387.
- (13) Aminzai, M. T.; Yabalak, E. Advanced polymeric membranes for environmental remediation: emerging roles of hydrochar and biochar composites. *Journal of Materials Science* **2025**, *60* (40), 18710-18733. DOI: 10.1007/s10853-025-11508-y.
- (14) Madhushree, M.; Vairavel, P.; Mahesha, G. T.; Bhat, K. S. A Comprehensive Review of Cellulose and Cellulose-Based Materials: Extraction, Modification, and Sustainable Applications. *J Nat Fibers* **2024**, *21* (1). DOI: 10.1080/15440478.2024.2418357.
- (15) Klemm, D.; Heublein, B.; Fink, H. P.; Bohn, A. Cellulose: Fascinating biopolymer and sustainable raw material. *Angew Chem Int Edit* **2005**, *44* (22), 3358-3393. DOI: 10.1002/anie.200460587.
- (16) Aziz, T.; Farid, A.; Haq, F.; Kiran, M.; Ullah, A.; Zhang, K. C.; Li, C.; Ghazanfar, S.; Sun, H. Y.; Ullah, R.; et al. A Review on the Modification of Cellulose and Its Applications. *Polymers* **2022**, *14* (15). DOI: 10.3390/polym14153206.
- (17) Thomas, B.; Raj, M. C.; Athira, K. B.; Rubiyah, M. H.; Joy, J.; Moores, A.; Drisko, G. L.; Sanchez, C. Nanocellulose, a Versatile Green Platform: From Biosources to Materials and Their Applications. *Chemical Reviews* **2018**, *118* (24), 11575-11625. DOI: 10.1021/acs.chemrev.7b00627.
- (18) Zhang, F.; Xu, K.; Bai, Y. A.; Wang, P. X. Multifunctional cellulose paper-based materials. *Cellulose* **2023**, *30* (14), 8539-8569. DOI: 10.1007/s10570-023-05426-y.



- (19) Liyanage, S.; Acharya, S.; Parajuli, P.; Shamshina, J. L.; Abidi, N. Production and Surface Modification of Cellulose Bioproducts. *Polymers* **2021**, *13* (19). DOI: 10.3390/polym13193433.
- (20) Yang, L.; Yuan, Q. Y.; Lou, C. W.; Lin, J. H.; Li, T. T. Recent Research Progress of Polysaccharide Polymer Coatings for Improving Properties of Paper-Based Packaging Materials. *Coatings* **2025**, *15* (3). DOI: 10.3390/coatings15030326.
- (21) Solberg, A.; Zehner, J.; Somorowsky, F.; Rose, K.; Korpela, A.; Syverud, K. Material properties and water resistance of inorganic-organic polymer coated cellulose paper and nanopaper. *Cellulose* **2023**, *30* (2), 1205-1223. DOI: 10.1007/s10570-022-04925-8.
- (22) Mujtaba, M.; Lipponen, J.; Ojanen, M.; Puttonen, S.; Vaittinen, H. Trends and challenges in the development of bio-based barrier coating materials for paper/cardboard food packaging; a. *Sci Total Environ* **2022**, *851*. DOI: 10.1016/j.scitotenv.2022.158328.
- (23) Islam, M. D.; Uddin, F. J.; Rashid, T. U.; Shahruzzaman, M. Cellulose acetate-based membrane for wastewater treatment-A state-of-the-art review. *Mater Adv* **2023**, *4* (18), 4054-4102. DOI: 10.1039/d3ma00255a.
- (24) Lee, J.; Luo, H.; Chen, Y. Y.; Ilestad, K.; Yu, D.; Ybarra, M.; Ma, C. Paper-Based Microfluidics for Tissue Engineering and Regenerative Medicine. *Cells Tissues Organs* **2025**. DOI: 10.1159/000545248.
- (25) Sheraz, M.; Sun, X. F.; Siddiqui, A.; Wang, Y. K.; Hu, S. H.; Sun, R. Cellulose-Based Electrochemical Sensors. *Sensors-Basel* **2025**, *25* (3). DOI: 10.3390/s25030645.
- (26) Lin, C. M.; Pei, Z. H.; Chen, J.; Lan, J. X.; Huang, H.; Ma, X. J.; Cao, S. L. An Eco-friendly Cellulose Paper-Based Tactile Sensor Driven by the Triboelectric Effect. *Acs Appl Polym Mater* **2025**, *7* (3), 1225-1235. DOI: 10.1021/acsapm.4c02682.
- (27) Huang, M. L.; Tang, Y. J.; Wang, X. Y.; Zhu, P.; Chen, T. Y.; Zhou, Y. M. Preparation of polyaniline/cellulose nanocrystal composite and its application in surface coating of cellulosic paper. *Prog Org Coat* **2021**, *159*. DOI: 10.1016/j.porgcoat.2021.106452.
- (28) Wang, L.; Kelly, P. V.; Ozveren, N.; Zhang, X. F.; Korey, M.; Chen, C.; Li, K.; Bhandari, S.; Tekinalp, H.; Zhao, X. H.; et al. Multifunctional polymer composite coatings and adhesives by incorporating cellulose nanomaterials. *Matter-Us* **2023**, *6* (2), 344-372. DOI: 10.1016/j.matt.2022.11.024.
- (29) Plank, M.; Hartmann, F.; Kuttich, B.; Kraus, T.; Gallei, M. Self-assembly of amphiphilic poly(2-hydroxyethyl methacrylate)-containing block copolymers in the vicinity of cellulose fibres. *European Polymer Journal* **2020**, *141*. DOI: 10.1016/j.eurpolymj.2020.110059.
- (30) Gemmer, L.; Hu, Q. W.; Niebuur, B. J.; Kraus, T.; Balzer, B. N.; Gallei, M. A block copolymer templated approach for the preparation of nanoporous polymer structures and cellulose fiber hybrids by ozone treatment. *Polymer Chemistry* **2022**, *13* (27), 4028-4046. DOI: 10.1039/d2py00562j.
- (31) Frieß, F. V.; Hartmann, F.; Gemmer, L.; Pieschel, J.; Niebuur, B. J.; Faust, M.; Kraus, T.; Presser, V.; Gallei, M. Thermo-Responsive Ultrafiltration Block Copolymer Membranes Based on Polystyrene-block-Poly(diethyl acrylamide). *Macromolecular Materials and Engineering* **2023**. DOI: 10.1002/mame.202300113.
- (32) Clodt, J. I.; Filiz, V.; Rangou, S.; Buhr, K.; Abetz, C.; Höche, D.; Hahn, J.; Jung, A.; Abetz, V. Double Stimuli-Responsive Isoporous Membranes via Post-Modification of pH-Sensitive Self-Assembled Diblock Copolymer Membranes. *Advanced Functional Materials* **2012**, *23* (6), 731-738. DOI: 10.1002/adfm.201202015.
- (33) Hub, L.; Koll, J.; Buhr, K.; Radjabian, M.; Abetz, V. pH-responsive size- and charge-selective block copolymer membrane for the separation of small proteins. *Journal of Membrane Science* **2024**, *708*. DOI: 10.1016/j.memsci.2024.123021.
- (34) Luo, X.; Wang, Z. Q.; Yan, M. X.; Xin, J. H.; Yang, Y. Q. One-pot three-step synthesis of PDMAEMA-PMMA-PNIPAM triblock block copolymer for preparing pH and thermal dual-responsive PVDF blend membranes. *Polym Eng Sci* **2023**, *63* (10), 3343-3352. DOI: 10.1002/pen.26448.
- (35) Nunes, S. P.; Behzad, A. R.; Hooghan, B.; Sougrat, R.; Karunakaran, M.; Pradeep, N.; Vainio, U.; Peinemann, K. V. Switchable pH-responsive polymeric membranes prepared via block copolymer micelle assembly. *ACS Nano* **2011**, *5* (5), 3516-3522. DOI: 10.1021/nn200484v From NLM Medline.
- (36) Shu, Z.; Li, H. Z.; Shi, Y.; Zuo, D. Y.; Yi, Z.; Gao, C. J. Dual sugar and temperature responsive isoporous membranes for protein sieving with improved separation coefficient and decreased denaturation. *Journal of Membrane Science* **2023**, *672*. DOI: 10.1016/j.memsci.2023.121450.



- (37) Rittner, T.; Pusse, S.; Bossmann, B.; Staudt, K.; Haben, A.; Kautenburger, R.; Beck, H. P.; Gallei, M. Metallopolymer-based block copolymers for perfluorinated substances (PFAS) and ion removal. *Journal of Materials Chemistry C* **2024**, *12* (47), 19116-19129. DOI: 10.1039/d4tc03546a.
- (38) Zhang, Z. Z.; Rahman, M. M.; Bajer, B.; Scharnagl, N.; Abetz, V. Highly selective isoporous block copolymer membranes with tunable polyelectrolyte brushes in soft nanochannels. *Journal of Membrane Science* **2022**, *646*. DOI: 10.1016/j.memsci.2022.120266.
- (39) Miyoshi, Y.; Nakata, Y.; Kitagawa, T.; Matsuyama, H.; Yoshioka, T.; Nakagawa, K. Effect of Surface Modification of Polyamide-Based Reverse Osmosis Membranes by Glycerol Monoacrylate-Butyl Acrylate Copolymers on Antifouling. *Industrial & Engineering Chemistry Research* **2024**, *63* (9), 4124-4133. DOI: 10.1021/acs.iecr.4c00153.
- (40) Zhao, C.; Li, L.; Wang, Q.; Yu, Q.; Zheng, J. Effect of film thickness on the antifouling performance of poly(hydroxy-functional methacrylates) grafted surfaces. *Langmuir* **2011**, *27* (8), 4906-4913. DOI: 10.1021/la200061h From NLM Medline.
- (41) Schöttner, S.; Brodrecht, M.; Uhlein, E.; Dietz, C.; Breitzke, H.; Tietze, A. A.; Buntkowsky, G.; Gallei, M. Amine-Containing Block Copolymers for the Bottom-Up Preparation of Functional Porous Membranes. *Macromolecules* **2019**, *52* (7), 2631-2641. DOI: 10.1021/acs.macromol.8b02758.
- (42) Wang, J. L.; Rahman, M. M.; Abetz, C.; Abetz, V. Bovine serum albumin selective integral asymmetric isoporous membrane. *Journal of Membrane Science* **2020**, *604*. DOI: 10.1016/j.memsci.2020.118074.
- (43) Peinemann, K. V.; Abetz, V.; Simon, P. F. Asymmetric superstructure formed in a block copolymer via phase separation. *Nat Mater* **2007**, *6* (12), 992-996. DOI: 10.1038/nmat2038 From NLM PubMed-not-MEDLINE.
- (44) Tsaour, L.; Wiesner, U. B. Non-Equilibrium Block Copolymer Self-Assembly Based Porous Membrane Formation Processes Employing Multicomponent Systems. *Polymers (Basel)* **2023**, *15* (9). DOI: 10.3390/polym15092020 From NLM PubMed-not-MEDLINE.
- (45) Gallei, M.; Rangou, S.; Filiz, V.; Buhr, K.; Bolmer, S.; Abetz, C.; Abetz, V. The Influence of Magnesium Acetate on the Structure Formation of Polystyrene-block-poly(4-vinylpyridine)-Based Integral-Asymmetric Membranes. *Macromolecular Chemistry and Physics* **2013**, *214* (9), 1037-1046. DOI: 10.1002/macp.201200708.
- (46) Frieß, F. V.; Hu, Q.; Mayer, J.; Gemmer, L.; Presser, V.; Balzer, B. N.; Gallei, M. Nanoporous Block Copolymer Membranes with Enhanced Solvent Resistance Via UV-Mediated Cross-Linking Strategies. *Macromol Rapid Commun* **2022**, *43* (3), e2100632. DOI: 10.1002/marc.202100632 From NLM Medline.
- (47) Gemmer, L.; Niebuur, B.-J.; Dietz, C.; Rauber, D.; Plank, M.; Frieß, F. V.; Presser, V.; Stark, R. W.; Kraus, T.; Gallei, M. Polyacrylonitrile-containing amphiphilic block copolymers: self-assembly and porous membrane formation. *Polymer Chemistry* **2023**, *14* (42), 4825-4837. DOI: 10.1039/d3py00836c.
- (48) Plank, M.; Frieß, F. V.; Bitsch, C. V.; Pieschel, J.; Reitenbach, J.; Gallei, M. Modular Synthesis of Functional Block Copolymers by Thiol-Maleimide "Click" Chemistry for Porous Membrane Formation. *Macromolecules* **2023**, *56* (4), 1674-1687. DOI: 10.1021/acs.macromol.2c02255.
- (49) Pusse, S.; Niebuur, B. J.; Kraus, T.; Presser, V.; Balzer, B. N.; Gallei, M. Synthesis and Self-Assembly of Pore-Forming Three-Arm Amphiphilic Block Copolymers. *Macromol Rapid Commun* **2025**, e2500077. DOI: 10.1002/marc.202500077 From NLM Publisher.
- (50) Heinz, S.; Gemmer, L.; Janka, O.; Gallei, M. Ferrocene-Modified Polyacrylonitrile-Containing Block Copolymers as Preceramic Materials. *Polymers (Basel)* **2024**, *16* (15). DOI: 10.3390/polym16152142 From NLM PubMed-not-MEDLINE.
- (51) Schöttner, S.; Hossain, R.; Ruttiger, C.; Gallei, M. Ferrocene-Modified Block Copolymers for the Preparation of Smart Porous Membranes. *Polymers (Basel)* **2017**, *9* (10). DOI: 10.3390/polym9100491 From NLM PubMed-not-MEDLINE.
- (52) Schöttner, S.; Schaffrath, H.-J.; Gallei, M. Poly(2-hydroxyethyl methacrylate)-Based Amphiphilic Block Copolymers for High Water Flux Membranes and Ceramic Templates. *Macromolecules* **2016**, *49* (19), 7286-7295. DOI: 10.1021/acs.macromol.6b01803.
- (53) Saleem, S.; Rangou, S.; Abetz, C.; Filiz, V.; Abetz, V. Isoporous Membranes from Novel Polystyrene-b-poly(4-vinylpyridine)-b-poly(solketal methacrylate) (PS-b-P4VP-b-PSMA) Triblock Terpolymers and Their Post-Modification. *Polymers (Basel)* **2019**, *12* (1). DOI: 10.3390/polym12010041 From NLM PubMed-not-MEDLINE.
- (54) Alward, D. B.; Kinning, D. J.; Thomas, E. L.; Fetters, L. J. Effect of Arm Number and Arm Molecular-Weight on the Solid-State Morphology of Poly(Styrene-Isoprene) Star Block Copolymers. *Macromolecules* **1986**, *19* (1), 215-224. DOI: DOI 10.1021/ma00155a034.



- (55) Kinning, D. J.; Thomas, E. L.; Alward, D. B.; Fetters, L. J.; Handlin, D. L. Sharpness of the functionality-induced structural transition in poly(styrene-isoprene) star block copolymers. *Macromolecules* **2002**, *19* (4), 1288-1290. DOI: 10.1021/ma00158a067.
- (56) Thomas, E. L.; Alward, D. B.; Kinning, D. J.; Martin, D. C.; Handlin, D. L.; Fetters, L. J. Ordered Bicontinuous Double-Diamond Structure of Star Block Copolymers - a New Equilibrium Microdomain Morphology. *Macromolecules* **1986**, *19* (8), 2197-2202. DOI: DOI 10.1021/ma00162a016.
- (57) Matsen, M. W. Effect of Architecture on the Phase Behavior of AB-Type Block Copolymer Melts. *Macromolecules* **2012**, *45* (4), 2161-2165. DOI: 10.1021/ma202782s.
- (58) Leibler, L. Theory of Microphase Separation in Block Copolymers. *Macromolecules* **1980**, *13* (6), 1602-1617. DOI: 10.1021/ma60078a047.
- (59) Upadhyaya, L.; Semsarilar, M.; Nehache, S.; Deratani, A.; Quemener, D. Filtration membranes from self-assembled block copolymers - a review on recent progress. *Eur Phys J-Spec Top* **2015**, *224* (9), 1883-1897. DOI: 10.1140/epjst/e2015-02507-7.
- (60) Li, L.; Szewczykowski, P.; Clausen, L. D.; Hansen, K. M.; Jonsson, G. E.; Ndoni, S. Ultrafiltration by gyroid nanoporous polymer membranes. *Journal of Membrane Science* **2011**, *384* (1-2), 126-135. DOI: 10.1016/j.memsci.2011.09.012.
- (61) Park, S.; Kim, Y.; Ahn, H.; Kim, J. H.; Yoo, P. J.; Ryu, D. Y. Giant Gyroid and Templates from High-Molecular-Weight Block Copolymer Self-assembly. *Sci Rep* **2016**, *6*, 36326. DOI: 10.1038/srep36326 From NLM PubMed-not-MEDLINE.
- (62) Gutmann, T.; Kumari, B.; Zhao, L.; Breitzke, H.; Schöttner, S.; Rüttiger, C.; Gallei, M. Dynamic Nuclear Polarization Signal Amplification as a Sensitive Probe for Specific Functionalization of Complex Paper Substrates. *The Journal of Physical Chemistry C* **2017**, *121* (7), 3896-3903. DOI: 10.1021/acs.jpcc.6b11751.
- (63) Höfler, M. V.; Lins, J.; Seelinger, D.; Pachernegg, L.; Schäfer, T.; Spirk, S.; Biesalski, M.; Gutmann, T. DNP enhanced solid-state NMR – A powerful tool to address the surface functionalization of cellulose/paper derived materials. *Journal of Magnetic Resonance Open* **2024**, *21*. DOI: 10.1016/j.jmro.2024.100163.
- (64) Kyeremateng, S. O.; Amado, E.; Kressler, J. Synthesis and characterization of random copolymers of (2,2-dimethyl-1,3-dioxolan-4-yl)methyl methacrylate and 2,3-dihydroxypropyl methacrylate. *European Polymer Journal* **2007**, *43* (8), 3380-3391. DOI: 10.1016/j.eurpolymj.2007.04.048.
- (65) Huang, E.; Skoufis, A.; Denning, T.; Qi, J.; Dagastine, R.; Tabor, R.; Berry, J. OpenDrop: Open-source software for pendant drop tensiometry contact angle measurements. *Journal of Open Source Software* **2021**, *6* (58). DOI: 10.21105/joss.02604.
- (66) Fulmer, G. R.; Miller, A. J. M.; Sherden, N. H.; Gottlieb, H. E.; Nudelman, A.; Stoltz, B. M.; Bercaw, J. E.; Goldberg, K. I. NMR Chemical Shifts of Trace Impurities: Common Laboratory Solvents, Organics, and Gases in Deuterated Solvents Relevant to the Organometallic Chemist. *Organometallics* **2010**, *29* (9), 2176-2179. DOI: 10.1021/om100106e.
- (67) Limprasart, W.; Höfler, M. V.; Kunzmann, N.; Rösler, L.; Herr, K.; Breitzke, H.; Gutmann, T. Peptides as Model Systems for Biofunctionalizations of Cellulose—Synthesis and Structural Characterization by Advanced Solid-State Nuclear Magnetic Resonance Techniques. *The Journal of Physical Chemistry C* **2023**, *127* (45), 22129-22138. DOI: 10.1021/acs.jpcc.3c05068.
- (68) Bennett, A. E.; Rienstra, C. M.; Auger, M.; Lakshmi, K. V.; Griffin, R. G. Heteronuclear decoupling in rotating solids. *The Journal of Chemical Physics* **1995**, *103* (16), 6951-6958. DOI: 10.1063/1.470372.
- (69) Brodrecht, M.; Kumari, B.; Thankamony, A.; Breitzke, H.; Gutmann, T.; Buntkowsky, G. Structural Insights into Peptides Bound to the Surface of Silica Nanopores. *Chemistry* **2019**, *25* (20), 5214-5221. DOI: 10.1002/chem.201805480 From NLM Medline.
- (70) Gallei, M.; Klein, R.; Rehahn, M. Silacyclobutane-Mediated Re-Activation of "Sleeping" Polyvinylferrocene Macro-Anions: A Powerful Access to Novel Metalloblock Copolymers. *Macromolecules* **2010**, *43* (4), 1844-1854. DOI: 10.1021/ma902092j.
- (71) Baskaran, D. Strategic developments in living anionic polymerization of alkyl (meth)acrylates. *Prog Polym Sci* **2003**, *28* (4), 521-581. DOI: 10.1016/s0079-6700(02)00083-7.
- (72) Hartmann, F.; Dockhorn, R.; Pusse, S.; Niebuur, B. J.; Koch, M.; Kraus, T.; Schiesser, A.; Balzer, B. N.; Gallei, M. Design and Self-Assembly of Second-Generation Dendrimer-like Block Copolymers. *Macromolecules* **2024**, *57* (15), 7098-7111. DOI: 10.1021/acs.macromol.4c00944.



- (73) Hartmann, F.; Niebuur, B. J.; Koch, M.; Kraus, T.; Gallei, M. Synthesis and microphase separation of dendrimer-like block copolymers by anionic polymerization strategies. *European Polymer Journal* **2023**, *187*. DOI: 10.1016/j.eurpolymj.2023.111894.
- (74) Villalobos, L. F.; Karunakaran, M.; Peinemann, K. V. Complexation-induced phase separation: preparation of composite membranes with a nanometer-thin dense skin loaded with metal ions. *Nano Lett* **2015**, *15* (5), 3166-3171. DOI: 10.1021/acs.nanolett.5b00275 From NLM Medline.
- (75) Nunes, S. P.; Karunakaran, M.; Pradeep, N.; Behzad, A. R.; Hooghan, B.; Sougrat, R.; He, H.; Peinemann, K. V. From micelle supramolecular assemblies in selective solvents to isoporous membranes. *Langmuir* **2011**, *27* (16), 10184-10190. DOI: 10.1021/la201439p From NLM Medline.
- (76) Steube, M.; Plank, M.; Gallei, M.; Frey, H.; Floudas, G. Building Bridges by Blending: Morphology and Mechanical Properties of Binary Tapered Diblock/Multiblock Copolymer Blends. *Macromolecular Chemistry and Physics* **2021**, *222* (4). DOI: 10.1002/macp.202000373.
- (77) Schellnhuber, K.; Blass, J.; Hubner, H.; Gallei, M.; Bennewitz, R. Single-Polymer Friction Force Microscopy of dsDNA Interacting with a Nanoporous Membrane. *Langmuir* **2024**, *40* (1), 968-974. DOI: 10.1021/acs.langmuir.3c03190 From NLM PubMed-not-MEDLINE.
- (78) Gunda, N. S. K.; Singh, M.; Norman, L.; Kaur, K.; Mitra, S. K. Optimization and characterization of biomolecule immobilization on silicon substrates using (3-aminopropyl)triethoxysilane (APTES) and glutaraldehyde linker. *Applied Surface Science* **2014**, *305*, 522-530. DOI: 10.1016/j.apsusc.2014.03.130.
- (79) Li, Y. S.; Vecchio, N. E.; Lu, W. Infrared and Raman spectra of (3,3,3-trifluoropropyl)trimethoxysilane, its sol and xerogel. *Spectrochim Acta A Mol Biomol Spectrosc* **2013**, *105*, 213-217. DOI: 10.1016/j.saa.2012.12.022 From NLM Medline.
- (80) Elbert, J.; Gallei, M.; Rüttiger, C.; Brunsen, A.; Didzoleit, H.; Stühn, B.; Rehahn, M. Ferrocene Polymers for Switchable Surface Wettability. *Organometallics* **2013**, *32* (20), 5873-5878. DOI: 10.1021/om400468p.
- (81) Foroutani, K.; Ghasemi, S. M.; Pourabbas, B. Ordered isoporous membranes from ionic diblock copolymers via SNIPS: Optimizing effective factors with a structural survey. *Prog Org Coat* **2021**, *161*. DOI: 10.1016/j.porgcoat.2021.106554.



Data Availability Statement: The data that support the findings of this study are available from the corresponding author upon request.

View Article Online
DOI: 10.1039/D5PY01203A

