

CrossMark
click for updatesCite this: *Chem. Sci.*, 2016, 7, 4167

Noble-metal-free Co_3S_4 -S/G porous hybrids as an efficient electrocatalyst for oxygen reduction reaction†

Wenling Gu,^{ac} Liuyong Hu,^{bc} Wei Hong,^{ac} Xiaofang Jia,^a Jing Li^{*a} and Erkang Wang^{*a}

Developing of a new noble-metal-free catalyst to replace Pt-based catalysts of the oxygen reduction reaction (ORR) both in alkaline and acidic conditions is extremely significant for the fuel cell. In this paper, based on the pyrolysis of an inexpensive precursor cobalt dithiolene (a S_4 -chelate complex) on simultaneously reduced graphene oxide (GO) as a support matrix, a high-efficiency noble-metal-free hybrid for oxygen reduction reaction (ORR) consisting of Co_3S_4 nanoparticles encapsulated in porous sulfur doped graphene (referred as Co_3S_4 -S/G) was fabricated. The catalyst obtained at 800 °C (Co_3S_4 -S/G-800) manifests excellent oxygen reduction activity. Of note, the Co_3S_4 -S/G-800 hybrids also exhibited prominent ORR activity with high selectivity (mainly 4e^- reaction process) and very low H_2O_2 yield in acidic electrolyte. The optimal Co_3S_4 -S/G-800 hybrid displayed much greater tolerance to methanol and higher stability than that of Pt/C. These admirable performances endorse Co_3S_4 -S/G-800 electrocatalyst holding great potential for fuel cells. Meanwhile, this work also provides a simple and practical method to fabricate cobalt chalcogenides by using the cost-effective and easily synthesized S_4 -chelate complex.

Received 25th January 2016

Accepted 2nd March 2016

DOI: 10.1039/c6sc00357e

www.rsc.org/chemicalscience

Introduction

With the rapid development of technology energy demand grows continuously. As a high energy-conversion efficiency technique, fuel cells have attracted much attention in recent years.¹ The oxygen reduction reaction (ORR) is a crucial step in high energy-conversion devices. However, the sluggish cathodic reaction of ORR often needs the assistance of an efficient electrocatalyst.² Among these electrocatalysts, Pt and Pt-based alloy materials³⁻⁵ have exhibited remarkable performance for ORR. Nevertheless, their high price, their scarcity, and especially low stability for methanol crossover have limited their widespread use.⁶ Correspondingly, much effort has been made to design and synthesize non-precious metal electrocatalysts (NPMCs) as alternatives to Pt, such as heteroatom-doped carbon materials, metal- N_x macrocycles, metal oxides supported on graphene, metal chalcogenides *etc.*⁷⁻¹⁰ Since Jasinski discovered that cobalt phthalocyanine (an N_4 -chelate macrocycle) possessed good ORR activity in alkaline conditions,¹¹ metal- N_4 macrocycles based

catalysts ($\text{M-N}_4/\text{C}$) have received much attention owing to the highly active site of surface nitrogen associated with metal.¹²⁻²⁰ Müllen *et al.*¹³ made another attempt to obtain a $[\text{CoN}_4]_3/\text{C}$ electrocatalyst by using a new class of metal- N_4 macrocyclic complexes as a precursor, which showed high catalyst activity and durability for ORR in alkaline conditions. Niu's group¹⁴ had reported that by pyrolyzing a mixture of cyanocobalamin (an N_4 -chelate macrocycle, vitamin B12) and GO, an excellent electrocatalyst was fabricated with a positive onset potential and high durability for ORR in alkaline electrolyte. Although excellent activity of $\text{M-N}_4/\text{C}$ based catalysts has been obtained in alkaline conditions, only few of these catalysts were found to retain catalyst activity in acidic conditions, mostly owing to the low amounts of catalytic sites of these catalysts. Moreover, these macrocycles still suffer from high-price and complicated synthetic processes which significantly influences their practical application.

In this work, inspired by the excellent electrocatalytic activity of $\text{M-N}_4/\text{C}$ catalysts and the special structure of the N_4 -chelate macrocycles, we proposed to use the cost-effective and easily fabricated metal- S_4 complex of cobalt dithiolene as a cobalt and sulfur rich precursor for obtaining high-performance ORR catalysts for the first time. By facile pyrolysis of the cobalt dithiolene and GO (which acts as a support carbon matrix) at 800 °C, a non-precious metal electrocatalyst of Co_3S_4 nanoparticles encapsulated in porous sulfur-doped graphene (Co_3S_4 -S/G-800) was obtained. As far as we know, cobalt chalcogenides (such as Co_{1-x}S , CoS , Co_3S_4 , Co_9S_8) had been shown

^aState Key Laboratory of Electroanalytical Chemistry, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, Changchun, Jilin 130022, PR China. E-mail: ekwang@ciac.ac.cn

^bState Key Laboratory of Polymer Physics and Chemistry, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, Changchun, Jilin 130022, PR China

^cUniversity of the Chinese Academy of Sciences, Beijing, 100049, PR China

† Electronic supplementary information (ESI) available: Additional information: SEM image, EDX spectra, XPS survey spectra and supporting CVs, LSV analysis. See DOI: 10.1039/c6sc00357e



to display higher chemical stability, electrical conductivity and electrocatalytic activity than other metal chalcogenides.^{21,22} With such outstanding advantages, they have been extensively applied in many fields, such as optoelectronic devices, energy storage, magnetic devices and electrocatalysis. In addition, theoretical studies also predicted that cobalt chalcogenides have great potential in ORR.²³ However, most recently reported cobalt chalcogenide based ORR catalysts required complicated and time-consuming synthesis processes and showed far lower electrocatalytic activity than the commercial Pt/C catalyst. Herein, the obtained Co_3S_4 -S/G-800 hybrid was found to be a highly effective and robust catalyst to boost ORR. Co_3S_4 -S/G-800 also showed better electrochemical durability and tolerance toward methanol than commercial Pt/C. To our surprise, the ORR activity of Co_3S_4 -S/G-800 was superior to most recently reported cobalt sulfide nanoparticles or other heteroatom based electrocatalysts both in alkaline and acidic conditions.^{21–28} All these results demonstrate that the obtained Co_3S_4 -S/G-800 is a promising electrocatalyst for fuel cells and that the pure S_4 -chelate complex can be used to replace the high-price N_4 -chelate macrocycles (such as cyanocobalamin, phthalocyanine, porphyrins *etc.*) for designing high-performance ORR catalysts. Meanwhile, this work also provides a simple and practical method to fabricate cobalt chalcogenides.

Results and discussion

Fig. 1 depicts the chemical structure of the cobalt dithiolene (which can be easily obtained by a one-step process), the synthetic process of the Co_3S_4 -S/G and the corresponding photograph of the catalyst. It is well known that the carbonization temperature is a key factor to influence the performance of the catalysts on ORR, since a low pyrolysis temperature will facilitate the incorporation of activated elements into the carbon skeleton and a high temperature may effectively increase electrical conductivity of the catalysts.²⁹ Therefore, the catalysts were obtained at different pyrolysis temperatures to find the optimum pyrolysis condition. XRD was carried out to analyze the crystal structures of all the as-prepared catalysts at different temperatures. As shown in Fig. S3a,† the presence of a peak around 25° suggested that the ordered graphitic phase

was formed at high carbonization temperatures, which was beneficial for the electrical conductivity of the catalysts. Meanwhile, the obtained catalysts showed the typical crystal structure of Co_3S_4 with the peaks located at 18.38 , 30.01 , 35.6 , 46.6 , 52.3 and 54.4° , which correspond to the (111), (220), (311), (400), (511) and (440) planes (JCPDS file: #471738) respectively.

The properties of the derived catalysts were further analyzed by Raman spectra. From Fig. S3b,† two broad bands corresponding to the D-band ($\sim 1350\text{ cm}^{-1}$) and G-band ($\sim 1580\text{ cm}^{-1}$) were observed. The D-band is related to the vibrations of the sp^3 carbon atoms of disordered graphene nanosheets, while the G-band is attributed to the in-plane vibrations of sp^2 carbon atoms of graphite. The ratio of the D band to the G band (I_D/I_G) varied with the pyrolysis temperatures, with values of 0.967 (600°C), 0.985 (700°C), 1.00 (800°C) and 1.03 (900°C). The increased ratio of I_D/I_G proved that the disordered and significant edge sites had been successfully increased by raising the pyrolysis temperature which would effectively enhance the conductivity of the catalysts and help charge localization for O_2 chemisorption.³⁰

The morphology of the fabricated Co_3S_4 -S/G catalysts at different pyrolysis temperatures was studied using SEM. As observed in Fig. S4,† raising pyrolysis temperatures from 600 to 900°C , the Co_3S_4 nanoparticles were gradually generated and uniformly encased in the derived carbon skeleton. The elemental compositions of prepared Co_3S_4 -S/G catalysts were investigated by XPS and EDX. From Table S1,† the contents of cobalt and sulfur showed decreased trends with increasing pyrolysis temperatures. It is of note that the contents of cobalt and sulfur were found to be lower in the XPS data compared with EDX, which may be caused by the generated carbon layers around the Co_3S_4 nanoparticles at a higher pyrolysis temperature and the impermeability to carbon layers to XPS for analyzing the cobalt and sulfur elements. However, this phenomenon provided favorable stability to the catalyst in catalytic aspects, especially under some strict conditions. Based on previous reports, although the encapsulated Co_3S_4 nanoparticles in the carbon layers could not directly contact with the electrolyte, they could activate the outer carbon layers making them more active toward ORR.³¹

Moreover, in order to explore the influence of the as-obtained catalysts at different temperatures on ORR, the electrochemical experiments were first evaluated by CV and RRDE techniques in 0.1 M KOH (Fig. S5 and 6†) electrolyte. It should be noticed that by comparing the onset potential, half-wave potential as well as current density, the Co_3S_4 -S/G-800 exhibited superior catalytic activity than the samples prepared at other temperatures (Table S2†), implying that the catalyst obtained at 800°C showed the optimal synergetic effect between the excellent electrical conductivity of the support matrix and the added component. Fig. S7 and Table S3† display the Brunauer–Emmet–Teller (BET) surface areas of all the catalysts, and the Co_3S_4 -S/G-800 showed the largest surface area of $52.44\text{ m}^2\text{ g}^{-1}$. In addition, based on the Barrett–Joyner–Halenda (BJH) analysis, the Co_3S_4 -S/G-800 catalyst contained mesopores with a peak at 13 nm , which may exert essential transport ability for ORR relevant substances (O_2 , H^+/OH^- , H_2O) and provide more

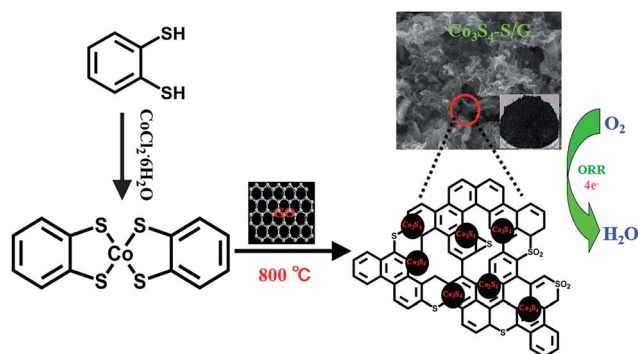


Fig. 1 Schematic illustration of the fabrication process of Co_3S_4 -S/G catalysts and electrocatalytic activity for oxygen reduction reaction.



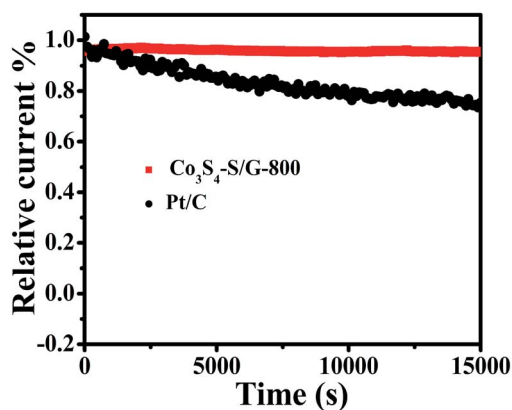


Fig. 6 Amperometric $i-t$ curves of $\text{Co}_3\text{S}_4\text{-S/G-800}$ and Pt/C in O_2 -saturated 0.1 M KOH electrolyte.

For commercialization, the durability and tolerance toward methanol is another important aspect for a fuel cell. As shown in Fig. S12 and 13,[†] almost no change of the LSV or CV curves was observed for $\text{Co}_3\text{S}_4\text{-S/G-800}$ both in alkaline and acidic conditions, indicating little effect of methanol on the catalyst. In contrast, an obvious change of the onset potential, half-wave potential and the ORR peak can be found for the Pt/C catalyst. These phenomena reveal that the $\text{Co}_3\text{S}_4\text{-S/G-800}$ catalyst was superior to the commercial Pt/C for methanol fuel cells. Since poor tolerance is a major obstacle of non-noble metal catalysts for fuel cells, especially in harsh acidic conditions,³⁶ it is essential to measure the stability of ORR catalysts. Herein, amperometric $i-t$ tests were carried out to measure the stability of the $\text{Co}_3\text{S}_4\text{-S/G-800}$ with a long time of 15 000 s. Impressively, as shown in Fig. 6 and S14,[†] after 15 000 s, the $\text{Co}_3\text{S}_4\text{-S/G-800}$ exhibited a relatively slower decay than the commercial Pt/C in both alkaline and acidic conditions. Moreover, by comparing recently reported cobalt sulfide nanoparticle based electrocatalysts, such as $\text{Co}_{1-x}\text{S/RGO}$ hybrid,²⁴ CoS_2 -based thin films²⁵ and $\text{CoS}_2/\text{N, S-GO}$,²⁶ the $\text{Co}_3\text{S}_4\text{-S/G-800}$ also showed a higher thermal stability. This result convincingly exemplifies that the $\text{Co}_3\text{S}_4\text{-S/G-800}$ catalyst has favorable stability. The fabricated $\text{Co}_3\text{S}_4\text{-S/G-800}$ catalyst with these excellent features may thus hold a promising potential for fuel cells.

Therefore, based on the characterization of the $\text{Co}_3\text{S}_4\text{-S/G-800}$ catalyst, the displayed prominent ORR activity could be attributed to these effects, (1) the high electric conduction of the support matrix; (2) the S-doped catalyst provides more favorable strains and defects for ORR; (3) the mesoporous structure in the $\text{Co}_3\text{S}_4\text{-S/G-800}$ exerts good transport ability for ORR relevant substances (O_2 , H^+/OH^- , H_2O) and provides more exposed active sites; (4) a synergistic effect between the S-doped graphene and Co_3S_4 nanoparticles.

Conclusions

In summary, we successfully prepared a metal- S_4 complex to replace traditional high-price N_4 -chelate macrocycles. From this a high-efficiency noble-metal-free catalyst $\text{Co}_3\text{S}_4\text{-S/G-800}$ was

synthesized on a large scale by a simple and facile annealing of the inexpensive precursor and GO at 800 °C. The as-prepared $\text{Co}_3\text{S}_4\text{-S/G-800}$ catalyst showed excellent ORR catalytic activity which was comparable with commercial Pt/C. Moreover, as a noble metal-free catalyst, the $\text{Co}_3\text{S}_4\text{-S/G-800}$ manifested obviously low methanol crossover effects, and robust stability in a long time test experiment. All these results demonstrate that the S_4 -chelate complex can serve as an effective precursor for designing the ORR catalyst, which opens up a new strategy to achieve highly efficient, stable, and low-cost ORR catalysts. Moreover, based on this work, an easy, economical and practical method to fabricate cobalt chalcogenides also was provided by using the pure S_4 -chelate complex as an efficient precursor.

Experimental

Chemicals and reagents

Graphite powder (spectral pure) was from Alfa Aesar (Ward Hill, MA, USA). Absolute ethanol, methanol, sulfuric acid (H_2SO_4) and potassium hydroxide (KOH) were purchased from Beijing Chemical Reagent (Beijing, China). 1,2-Benzenedithiol (TCI) and 20% E-TEK Pt/C were obtained from Alfa Aesar (Tianjin, China) and Millipore Mill-Q (18.2 M Ω cm) deionized water was used to prepare the aqueous solutions.

Apparatus

Transmission electron microscopy (TEM) images, high angle annular dark field-scanning transmission electron microscopy (HAADF-STEM) and elemental mapping images were recorded by a TECNAI G2 high-resolution transmission electron microscope (Hitachi, Tokyo, Japan) with an accelerating voltage of 200 kV. Energy dispersive X-ray (EDX) spectra and scanning electron microscope (SEM) images were measured with an XL30 ESEM FEG SEM (Philips, Netherlands) operating with an accelerating voltage of 20 kV. X-Ray photoelectron spectroscopy (XPS) analysis was obtained from an ESCALAB-MKII X-ray photoelectron spectroscope (VG Scientific, UK). Powder X-ray diffraction (XRD) was recorded by a D8 ADVANCE (Germany) using $\text{Cu-K}\alpha$ radiation ($\lambda = 1.5406 \text{ \AA}$). Raman spectra were recorded by a Renishaw 2000 model confocal microscopy Raman spectrometer (Renishaw Ltd., Gloucestershire, UK). Electrochemical impedance spectroscopy (EIS) was measured with an Autolab/PG30 electrochemical analyzer system (ECO Chemie B.V. Netherlands).

In addition, cyclic voltammetric (CV) and amperometric $i-t$ curves were carried out with a CH Instruments 800 voltammetric analyzer (Shanghai, China). Rotating ring-disk electrode (RRDE) and rotating disk electrode (RDE) measurements were made using a Model RRDE-3A Apparatus (ALS, Japan) coupled with a CH Instruments 800 electrochemical workstation. In the electrochemical experiments, the modified glassy carbon electrode with catalyst samples acted as the working electrode, with an Ag/AgCl (saturated KCl) electrode and a platinum wire as the reference electrode and counter electrode, respectively. All electrode potentials were referenced to the reversible hydrogen electrode (RHE) using the formula $E(\text{vs. RHE}) = E(\text{vs. Ag/AgCl})$



+ 0.197 + 0.059pH. In 0.1 M KOH solution (pH = 13), E (vs. RHE) = E (vs. Ag/AgCl) + 0.964, while, in 0.5 M H₂SO₄ electrolyte (pH = 0.25), E (vs. RHE) = E (vs. Ag/AgCl) + 0.212.

Preparation of the catalyst samples

As illustrated in Fig. S1,† the S₄-chelate complex of cobalt dithiolene was obtained by a previously reported method in a one-step process,³⁷ and the UV-Vis absorption spectrum (Fig. S2†) was used to characterize the compound. Then, in a typical synthesis of Co₃S₄-S/G-800 samples, 2 g cobalt dithiolene was dissolved into 100 mL absolute ethanol containing 2 mg mL⁻¹ GO (which was obtained by a modified Hummers' procedure³⁸) with ultrasonication and stirring until a homogeneous solution was obtained. Afterwards, the solvent was removed under reduced pressure, and the remaining powder was thermally annealed under flowing Ar at 180 and 800 °C for 1 and 2 h, respectively, with a heating rate of 5 °C min⁻¹. After that, the obtained black products were etched in 50 mL of 0.5 M H₂SO₄ solution for 24 h to remove unstable and inactive substance and then were washed three times with deionized water. The Co₃S₄-S/G-800 catalyst was obtained by drying the black product at 60 °C in a vacuum.

The comparative samples of pristine graphene, sulfur-doped graphene (S/G, pyrolysis of 1,2-benzenedithiol and GO at 800 °C), Co₃S₄/C-800 (pyrolysis of cobalt dithiolene complex without GO), S/G + Co₃S₄/C-800 (physical mixture) and the nanocatalysts which were carbonized at 600, 700 and 900 °C (designated as Co₃S₄-S/G-600, Co₃S₄-S/G-700 and Co₃S₄-S/G-900, respectively) were also prepared to better understand the catalytic properties for ORR.

Electrocatalytic activity measurements

Prior to each experiment, the working electrode was polished with 0.3 and 0.05 μm alumina slurries and cleaned with deionized water and absolute ethanol to obtain a mirror finish. The catalyst ink was prepared as follows: 4 mg catalyst sample was added into 1 mL of a mixed solution which contained 20 : 1 : 0.075 (v/v/v) of water, absolute ethanol and Nafion (5.0 wt%). Then the solution was sonicated for 30 min to obtain 4 mg mL⁻¹ catalyst. Before the experiments of CVs and amperometric i - t , 6 μL catalyst ink was dropped onto a glassy carbon electrode (GCE: 3.0 mm in diameter) with a loading amount of 0.34 mg cm⁻² and dried under an infrared lamp. The linear sweep voltammetry (LSV) measurements were recorded by using RRDE or RDE techniques to evaluate the electrocatalytic activity of different catalyst samples. In addition, the 20% E-TEK Pt/C catalyst was also prepared in the same way and dropped with a loading amount of 25 μg Pt cm⁻² as a comparison.

Before each experiment, the electrolyte was bubbled by purging high-purity N₂ gas for at least 30 min in order to remove dissolved oxygen. The modified working electrode was electrochemically treated and cleaned by CV sweeping (potential scan from 1.1 to 0 V (vs. RHE)) with a scan rate of 100 mV s⁻¹ in an N₂-saturated electrolyte until a reproducible curve was achieved. Meanwhile, CV curves in N₂-saturated or O₂-saturated solution were obtained by CV sweeping with a scan rate of 50 mV s⁻¹

after purging N₂ or O₂ at least for 30 min. The amperometric i - t curves were obtained by sweeping the Co₃S₄-S/G-800 or 20% E-TEK Pt/C (Pt/C) catalyst modified electrode over 15 000 s at a potential of 0.614 V (vs. RHE) in O₂-saturated 0.1 M KOH and 0.5 M H₂SO₄ solution.

Furthermore, in the RRDE experiments, the Pt ring potential was set at 1.264 V (vs. RHE) in 0.1 M KOH and 1.012 V (vs. RHE) in 0.5 M H₂SO₄. The transferred electron number (n) and the generated H₂O₂ can be calculated from the values of i_d (the current of disk electrode) and i_r (the current of ring current) using the following equations:³⁹

$$n = \frac{4i_d}{i_d + i_r/N} \quad (1)$$

$$\text{H}_2\text{O}_2\% = \frac{200i_r/N}{i_d + i_r/N} \quad (2)$$

where N is the collection efficiency of the ring electrode (0.42).

The RDE measurements were performed in O₂-saturated 0.1 M KOH or 0.5 M H₂SO₄ electrolyte by a negative-direction sweeping potential with a scan rate of 5 mV s⁻¹ under different electrode rotation rates. The electron transfer also can be estimated according to the Koutecky-Levich equations:

$$\frac{1}{j} = \frac{1}{j_k} + \frac{1}{B\omega^{0.5}} \quad (3)$$

$$B = 0.2nF(D_0)^{2/3}\nu^{-1/6}C_0 \quad (4)$$

where j represents the current density, j_k is the kinetic-limiting current density, ω is the electrode rotation rate, n is the transferred electron number, F is the Faraday constant of 96 485 C mol⁻¹, and D_0 is the diffusion coefficient of O₂ (1.9 × 10⁻⁵ cm² s⁻¹ in 0.1 M KOH and 1.4 × 10⁻⁵ cm² s⁻¹ in 0.5 M H₂SO₄), ν represents the kinematic viscosity of the electrolyte (0.01 cm² s⁻¹ both in 0.1 M KOH and 0.5 M H₂SO₄), C_0 is the bulk concentration of O₂ (1.2 × 10⁻⁶ mol cm⁻³ in 0.1 M KOH and 1.1 × 10⁻⁶ mol cm⁻³ in 0.5 M H₂SO₄).^{40,41}

Acknowledgements

This work was supported by National Natural Science Foundation of China with grant No. 21427811.

Notes and references

- 1 Y. Nie, L. Li and Z. D. Wei, *Chem. Soc. Rev.*, 2015, **44**, 2168.
- 2 H. A. Gasteiger and N. M. Marković, *Science*, 2009, **324**, 48.
- 3 J. B. Wu, A. Gross and H. Yang, *Nano Lett.*, 2011, **11**, 798.
- 4 V. R. Stamenkovic, B. Fowler, B. S. Mun, G. F. Wang and N. M. Markovic, *Science*, 2007, **315**, 493.
- 5 C. L. Zhang, W. Sandorf and Z. M. Peng, *ACS Catal.*, 2015, **5**, 2296.
- 6 D. S. Su and G. Sun, *Angew. Chem., Int. Ed.*, 2011, **50**, 11570.
- 7 D. Deng, X. Pan, L. Yu, Y. Cui, Y. Jiang, J. Qi, W. X. Li, Q. Fu, X. Ma, Q. Xue, G. Sun and X. Bao, *Chem. Mater.*, 2011, **23**, 1188.



- 8 G. Wu, K. L. More, C. M. Johnston and P. Zelenay, *Science*, 2011, **332**, 443.
- 9 Y. Liang, Y. Li, H. Wang, J. Zhou, J. Wang, T. Regier and H. Dai, *Nat. Mater.*, 2011, **10**, 780.
- 10 H. Wang, Y. Liang, Y. Li and H. Dai, *Angew. Chem., Int. Ed.*, 2011, **50**, 10969.
- 11 R. Jasinski, *Nature*, 1964, **201**, 1212.
- 12 Y. Y. Jiang, Y. Z. Lu, X. Y. Lu, D. X. Han, Q. X. Zhang, L. Niu and W. Chen, *ACS Catal.*, 2013, **3**, 1263.
- 13 R. L. Liu, C. Malotki, L. Arnold, N. Koshino, H. Higashimura, M. Baumgarten and K. Müllen, *J. Am. Chem. Soc.*, 2011, **133**, 10372.
- 14 Y. Y. Jiang, Y. Z. Lu, X. D. Wang, Y. Bao, W. Chen and L. Niu, *Nanoscale*, 2014, **6**, 15066.
- 15 W. M. Li, A. P. Yu, D. Higgins, B. Llanos and Z. W. Chen, *J. Am. Chem. Soc.*, 2010, **132**, 17056.
- 16 I. Hijazi, T. Bourgeteau, R. Cornut, A. Morozan, A. Filoramo, J. Leroy, V. Derycke, B. Joussetme and S. Campidelli, *J. Am. Chem. Soc.*, 2014, **136**, 6348.
- 17 P. J. Wei, G. Q. Yu, Y. Naruta and J. G. Liu, *Angew. Chem., Int. Ed.*, 2014, **53**, 6659.
- 18 Y. S. Zhu, B. S. Zhang, X. Liu, D. W. Wang and D. S. Su, *Angew. Chem., Int. Ed.*, 2014, **53**, 10673.
- 19 I. Hijazi, T. Bourgeteau, R. Cornut, A. Morozan, A. Filoramo, J. Leroy, V. Derycke, B. Joussetme and S. Campidelli, *J. Am. Chem. Soc.*, 2014, **136**, 6348.
- 20 H. Choi, N. Kumar and J. Baek, *Nanoscale*, 2015, **7**, 6991.
- 21 M. X. Shen, C. P. Ruan, Y. Chen, C. H. Jiang, K. L. Ai and L. H. Lu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 1207.
- 22 N. Mahmood, C. Z. Zhang, J. Jiang, F. Liu and Y. L. Hou, *Chem.-Eur. J.*, 2013, **19**, 5183.
- 23 R. A. Sidik and A. B. Anderson, *J. Phys. Chem. B*, 2006, **110**, 936.
- 24 H. L. Wang, Y. Y. Liang, Y. G. Li and H. J. Dai, *Angew. Chem., Int. Ed.*, 2011, **50**, 10969.
- 25 L. Zhu, D. Susac, M. Teo, K. C. Wong, P. C. Wong, R. R. Parsons, D. Bizzotto, K. R. Mitchell and S. A. Campbell, *J. Catal.*, 2008, **258**, 235.
- 26 T. Sun, Q. Wu, R. C. Che, Y. F. Bu, Y. F. Jiang, Y. Li, L. J. Yang, X. Z. Wang and Z. Hu, *ACS Catal.*, 2015, **5**, 3625.
- 27 K. P. Singh, E. J. Bae and J. S. Yu, *J. Am. Chem. Soc.*, 2015, **137**, 3165.
- 28 J. Liang, Y. Zheng, J. Chen, J. Liu, D. H. Jurcakova, M. Jaroniec and S. Z. Qiao, *Angew. Chem., Int. Ed.*, 2012, **51**, 3892.
- 29 L. Lin, Q. Zhu and A. W. Xu, *J. Am. Chem. Soc.*, 2014, **136**, 11027.
- 30 S. L. Zhao, H. J. Yin, L. Du, L. C. He, K. Zhao, L. Chang, G. P. Yin, H. J. Zhao, S. Q. Liu and Z. Y. Tang, *ACS Nano*, 2014, **8**, 12660.
- 31 Y. Hu, J. Q. Jensen, W. Zhang, L. N. Cleemann, W. Xing, N. J. Bjerrum and Q. Li, *Angew. Chem., Int. Ed.*, 2014, **53**, 3675.
- 32 Z. Y. Wu, X. X. Xu, B. C. Hu, H. W. Liang, Y. Lin, L. F. Chen and S. H. Yu, *Angew. Chem., Int. Ed.*, 2015, **54**, 8179.
- 33 Y. Chen, J. Li, T. Mei, X. G. Hu, D. W. Liu, J. C. Wang, M. Hao, J. H. Li, J. Y. Wang and X. B. Wang, *J. Mater. Chem. A*, 2014, **2**, 20714.
- 34 L. Zhu, D. Susac, M. Teo and K. Wong, *J. Catal.*, 2008, **258**, 235.
- 35 H. T. Liu, Y. Q. Liu and D. B. Zhu, *J. Mater. Chem.*, 2011, **21**, 3335.
- 36 W. X. Yang, Y. Q. Zhang, C. Y. Liu and J. B. Jia, *J. Power Sources*, 2015, **274**, 595.
- 37 W. McNamara, Z. J. Han, P. Alperin, W. Brennessel, P. Holland and R. Eisenberg, *J. Am. Chem. Soc.*, 2011, **133**, 15368.
- 38 W. S. Hummers and R. E. Offeman, *J. Am. Chem. Soc.*, 1958, **80**, 1339.
- 39 G. Ma, R. Jia, J. Zhao, Z. Wang, C. Song, S. Jia and Z. Zhu, *J. Phys. Chem. C*, 2011, **115**, 25148.
- 40 R. Z. Zhang, S. J. He, Y. Z. Lu and W. Chen, *J. Mater. Chem. A*, 2015, **3**, 3559.
- 41 M. Jahan, Z. L. Liu and K. Loh, *Adv. Funct. Mater.*, 2013, **23**, 5363.

