


Cite this: *Nanoscale Adv.*, 2019, 1, 4207

Hydrophobic ion pairing: encapsulating small molecules, peptides, and proteins into nanocarriers

Kurt D. Ristorph and Robert K. Prud'homme *

Hydrophobic ion pairing has emerged as a method to modulate the solubility of charged hydrophilic molecules ranging in class from small molecules to large enzymes. Charged hydrophilic molecules are ionically paired with oppositely-charged molecules that include hydrophobic moieties; the resulting uncharged complex is water-insoluble and will precipitate in aqueous media. Here we review one of the most prominent applications of hydrophobic ion pairing: efficient encapsulation of charged hydrophilic molecules into nano-scale delivery vehicles – nanoparticles or nanocarriers. Hydrophobic complexes are formed and then encapsulated using techniques developed for poorly-water-soluble therapeutics. With this approach, researchers have reported encapsulation efficiencies up to 100% and drug loadings up to 30%. This review covers the fundamentals of hydrophobic ion pairing, including nomenclature, drug eligibility for the technique, commonly-used counterions, and drug release of encapsulated ion paired complexes. We then focus on nanoformulation techniques used in concert with hydrophobic ion pairing and note strengths and weaknesses specific to each. The penultimate section bridges hydrophobic ion pairing with the related fields of polyelectrolyte coacervation and polyelectrolyte-surfactant complexation. We then discuss the state of the art and anticipated future challenges. The review ends with comprehensive tables of reported hydrophobic ion pairing and encapsulation from the literature.

Received 16th May 2019
Accepted 18th September 2019

DOI: 10.1039/c9na00308h

rsc.li/nanoscale-advances

1. Introduction, overview, and terminology

In the twenty years since Meyer and Manning's classic 1998 review,¹ hydrophobic ion pairing (HIP) has gained prominence as a useful strategy for making charged hydrophilic molecules into hydrophobic complexes. The technique has a number of applications and has been used, among others, to dissolve molecules in supercritical CO₂,² dissolve enzymes in organic solvents without losing activity,³ improve intestinal adsorption^{4–6} or skin permeation,^{7,8} or otherwise enhance bioavailability.⁹

This review will focus on one of the most prevalent uses of hydrophobic ion pairing: the complexation and encapsulation of charged hydrophilic small molecule, peptide, or protein therapeutics into drug delivery vehicles. The first section summarizes the general rules for hydrophobic ion pairing. We discuss drug eligibility and class-specific considerations, review commonly-used counterions, and outline key parameters such as counterion pK_a. The third section focuses on formulation techniques that have been used to encapsulate hydrophobic complexes into nanoparticles, microparticles, and emulsions for drug delivery. The fourth section discusses how ion paired drug payloads are released from their delivery vehicles. The fifth

section bridges the HIP technique with polyelectrolyte-polyelectrolyte complexation ('coacervation') and polyelectrolyte-surfactant complexation, related fields that have remained largely unconnected from the hydrophobic ion pairing literature. We do not review another related field, nucleotide complexation with cationic lipids to form lipoplexes or solid lipid nanoparticles, but provide references to a number of excellent reviews. At the end of the article we present tables to organize the reported results of hydrophobic ion pairing used for encapsulation. The tables are sorted by both therapeutic and counterion for easy reference and rapid comparison (Fig. 1).

Hydrophobic ion pairing is the process of forming ionic interactions¹⁰ between a charged hydrophilic molecule with an oppositely-charged counterion.¹ The counterion contains at least one hydrophobic domain such as an alkyl tail or aromatic ring. The complexation increases hydrophobicity by two main mechanisms: first, the molecule's natural charge is masked, mitigating solubility in polar solvents such as water. Second, the hydrophobic groups on the counterion, typically nonpolar aliphatic tails or aromatic groups, help to coat the original molecule's surface area with hydrophobic domains that exclude water.

For our purposes, the charged hydrophilic is a drug or dye and may be referred to as an 'active pharmaceutical ingredient (API)' or 'therapeutic.' The counterion is referred to in the literature as a 'hydrophobic counterion,' 'ion pair(ing agent) (IP),' or 'salt former.' Due to their amphiphilic chemical nature,

Department of Chemical and Biological Engineering, Princeton University, Princeton, New Jersey 08544, USA. E-mail: prudhomme@princeton.edu



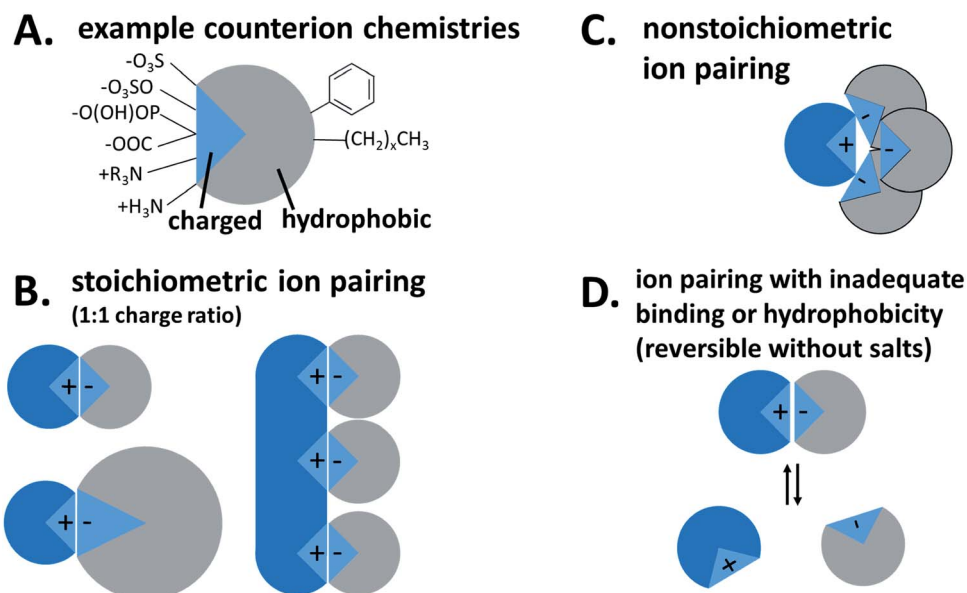


Fig. 1 Hydrophobic ion pairing schematic. (A) Possible charged groups (left) and hydrophobic moieties (right) for a counterion. (B) Stoichiometric ion pairing between a cationic API (blue) and anionic counterion. (C) Non-stoichiometric ion pairing. (D) Reversible ion pairing due to inadequate binding or hydrophobicity.

many hydrophobic counterions used are surfactants, so the term 'surfactant' may be used as well. The act of forming an ionic association between the two species is termed either 'hydrophobic ion pairing' or 'ionic complexation,' and the resulting paired species is a 'hydrophobic complex' or 'HIP complex.' We will discuss later why we do not use the term 'salt.'

Another important piece of terminology is the stoichiometry between the two species. In the HIP literature, there is no standard convention for reporting the ratio of hydrophilic therapeutic to counterion. Molar ratio (reported either as a ratio of $x:y$ or as a fraction), mass ratio, charge ratio, and N/P ratio – *i.e.* ratio of positive to negative charges, usually reported as a fraction, from the lipoplex literature – have all been used. Consider a 1300 Da peptide with five cationic groups that is paired with five molecules of a monovalent counterion of molecular weight 280 Da (Fig. 2A). Reporting ratios as drug-counterion, this complex has a molar ratio of 1 : 5 or 0.2, a mass ratio of 0.93, a charge ratio of 1 : 1, and an N/P ratio of 1. Charge and molar ratios are the most intuitive of these, and the $x : y$ ratio nomenclature is more intuitive than fractions.

We recommend that future researchers in the field use *charge ratios* and report the ratio as 'drug : counterion' rather than as a fraction. Charge ratio is a useful and intuitive parameter in HIP, and should be reported whenever possible. Both molecules' degrees of ionisation may vary with pH; when possible, the charge ratio should be reported at the pH of the complexation.¹¹ When describing the charge ratio of a system where one molecule is zwitterionic, researchers should note whether their reported charge ratio is based on the molecule's *net* charge or charge of *only one type*. We recommend the latter, but this is not always possible for large proteins, where only net charge can readily be determined. Consider the example above; if the peptide had one anionic group in addition to five cationic


groups, the charge ratio of peptide cations (5) to counterion anions (5) is still 1 : 1 (Fig. 2B). The peptide : counterion charge ratio calculated from the peptide's *net* charge of $(5-1)=4$, though, is 4 : 5 or 1 : 1.25, suggesting an excess of counterions when none actually exists. Reporting the molar ratio along with the charge ratio should clarify this point, provided an accurate counting of what charged groups exist on each species is included. In this review, we have converted reported stoichiometries into charge ratios to facilitate comparisons.

2. Hydrophobic ion pairing

Hydrophobic ion pairing is an attractive technique for encapsulating water-soluble therapeutics using formulation strategies optimized for water-insoluble drugs. These strategies are desirable because new strategies to encapsulate hydrophilic molecules in nano-scale delivery vehicles remain challenging.¹² Low drug loadings, poor encapsulation efficiencies, and a lack of scalability continue to prevent many liposome and nanoparticle formulations of biologic therapeutics from reaching the market.¹² The potential benefits of encapsulation – targeting, protection from enzymatic degradation, improved circulation time, enhanced bioavailability, controlled release, reduced toxicity, and overall improved drug performance – are strong driving motivations to develop scalable, highly-loaded formulations with high encapsulation efficiencies.^{13,14} This is particularly attractive for biologic (peptide and protein) therapeutics, whose circulation time unprotected in the blood may be as low as minutes.¹²

Nanoparticle formulation strategies for hydrophobic drugs have been developed to address the growing number of new, strongly hydrophobic therapeutics.^{15,16} These techniques – oil-in-water emulsions, nanoprecipitation, solid lipid nanoparticles, *etc.* – are designed to take advantage of a drug's





Modifying a drug's solubility profile to make it more hydrophobic for encapsulation is also the goal of some prodrug strategies;¹⁹ both techniques temporarily add hydrophobic groups to a hydrophilic molecule.²⁰ Unlike prodrug approaches, HIP does not modify any covalent bonds on the original API. This is important from a regulatory standpoint: prodrugs require full FDA approval but the requirements for hydrophobic ion pairs may not be as stringent, depending on the other changes made to the formulation.²¹

Mechanisms of solubilisation in aqueous solution. Why are molecules soluble or insoluble in aqueous solutions? Understanding the fundamental mechanisms of solubilization helps understand the principles behind HIP. The solubility or phase behaviour of a species is determined by entropy and enthalpy. Entropy is the state of disorder in a system and is determined by the statistical number of configurations a system can attain. For small molecules, that entropy is determined by the concentration of the solute in the solvent. The entropic contribution to the chemical potential for a dilute solute in an ideal system is $\mu_i^{\text{ideal}} = \mu_{i0} + kT \ln x_i$, where μ_i is the chemical potential (μ_{i0} is the chemical potential of the pure species) and x_i is the molar fraction of the solute. It can be seen that entropy always favours dissolution, *i.e.* increasing the degrees of freedom in the system is favoured.

Water is a unique solvent and is the strongest of the hydrogen bonding fluids. The polarity of the water molecule gives water a high dielectric constant: $\epsilon = 80$. This is in contrast to the dielectric constant of a hydrophobic oil phase (*e.g.* dodecane), which will have $\epsilon = 2$. The dielectric constant determines the strength of electrostatic interactions between elementary charges. The interaction energy between a positive and negative charge in solution is $F = \frac{k}{\epsilon} \frac{q_1 q_2}{r^2}$. As the dielectric constant increases, therefore, the force holding ions together decreases. Hydrophobic ion pairs stay insoluble in part because they usually include large nonpolar groups that exclude water from fully solvating the ionic-ionic interaction sites. The hydrophobic ion paired precipitate or core of a NC has a low dielectric constant, which magnifies the strength of the electrostatic attractions. This same concept arises in the protein literature, where the interactions between anionic and cationic peptides in the hydrophobic core of a globular protein enhance its stability. However, the same residues on the surface of a protein would enhance its water solubility. It often remains unclear if any water remains associated with the pair in a nanoparticle core; the best data addressing this question comes from studies of ionomers.²⁴⁻²⁷

Eligibility for hydrophobic ion pairing. For a therapeutic molecule to be eligible for HIP, it must contain at least one charged group. Many antibiotics contain amine groups that are

positively charged at physiological pH and can be used for this purpose. Anionic carboxylic acid groups are also commonly used as pairing sites in HIP. Molecules with a strong net charge or only one type of charge are the most straightforward to complex, since a single counterion species can be used. Zwitterionic molecules with both anionic and cationic charges present a more complicated challenge; here, shifting the solution pH to turn off one type of charge can be an effective strategy. This is presented in more detail below. Another consideration for HIP eligibility is the molecule's charge density (charge per molecular weight). Intuitively, adding a single hydrophobic counterion onto a small molecule that has a single charge and molecular weight approximately 300 Da will increase hydrophobicity more than adding the same single counterion to a peptide with one charge and a molecular weight of 3000 Da, *i.e.* the charge per surface area is lower on the larger molecule. Depending on the desired hydrophobicity of the final complex, a given charged molecule may have too low of a charge density, such that adding a hydrophobic counterion will not sufficiently increase hydrophobicity to affect precipitation.

We typically do not use or recommend using the term 'salt' to describe the complexes formed by hydrophobic ion pairing, because 'salts' are commonly understood to refer to crystalline assemblies of stoichiometric amounts of oppositely-charged ions. HIP complexes may be less crystalline than the original drug used,^{28–30} and non-stoichiometric charge ratios are common.

We pause here to briefly address the field of nucleic acid encapsulation and delivery. Nucleic acids – plasmid DNA, linear DNA, siRNA, mRNA, *etc.* – have been packaged into solid lipid nanoparticles (SLNs) or lipoplexes through ionic complexation between cationic lipids and the nucleic acid's anionic phosphate backbone. This strategy shares a number of similarities with hydrophobic ion pairing, with a few notable exceptions. The most significant is that the regular charge along the phosphate backbone gives nucleic acids a strong, uniform charge density along the molecule. This is different from the small molecule, peptide and protein therapeutics discussed here, which often have less ordered regions of hydrophobicity and hydrophilicity/charge. For the reader familiar with HIP but not SLNs/lipoplexes, we recommend a number of reviews.^{31–37}

Common counterions. Because the counterions used for hydrophobic ion pairing should contain at least one charged group and at least one hydrophobic domain, ionic surfactants are common. These may be either anionic or cationic and typically contain either one or two charged groups. Fatty acids or other carboxylic acid-containing surfactants such as oleic acid, stearic acid, or deoxycholic acid, or their sodium salts, have been extensively used. Pamoic acid, which has two carboxylic acid groups, has been effective in cases where fatty acids were not.³⁸ Sulfates are also popular, most frequently sodium dodecyl sulfate and sodium docusate. Two-tailed phospholipids such as dimyristoyl phosphatidyl glycerol have been used as well. Anionic polymers such as dextran sulfate have also been investigated, most frequently for complexation with multivalent peptide or protein therapeutics. Though HIP language has been used to describe this kind of polyelectrolyte

complexation, the mechanisms differ in important ways. That distinction is the subject of Section 5 of this review (Table 1).

The most common cations in the HIP literature are quaternary amines and alkylamines (see Table 2). Quaternary amines are permanently charged, so complexation is possible over a wider range of pH values than primary, secondary, or tertiary amines. The permanent charge is usually cytotoxic, and using quaternary amines adds toxicity to otherwise nontoxic formulations.³⁹ A wide variety of quaternary amines is commercially available, with varying lengths and numbers of alkyl tails that lead to an easily tuneable range of hydrophobicities.⁴⁰ Researchers have recently reported efforts to synthesize arginine-based cationic surfactants for HIP, which should be both biodegradable and non-cytotoxic.⁴¹

Specific considerations by drug molecule class

Small molecules. Many small molecule drugs have only one ionic group. Depending on the pK_a of the ionic group and the drug's solubility, HIP is relatively straightforward and can be carried out in water. In a typical 'pre-forming' scenario for hydrophilic small molecules, the drug and counterion are each dissolved in water and mixed to form a precipitate.^{11,42} It is worth noting that small molecules with ionizable groups may be manufactured either as a salt or in the free acid/base form. The free acid/base is usually less soluble in water than the salt, but might not be hydrophobic enough for a desired encapsulation strategy.⁴³ Since species must be charged in order to ion pair, salt forms of the drug and hydrophobic counterion may be preferred. When the drug is manufactured in the free acid/base form, conversion to a readily-dissociating salt form (*e.g.* mesylate, ammonium, or sodium) before HIP may assist complexation. A drawback of this approach is that it increases the solution's overall ionic strength, which can drive decomplexation and drug release from a delivery vehicle by ion exchange.^{38,44,45} Researchers should examine the effect of ionic strength on their specific systems to determine if one charge equivalent of soluble counterions such as sodium or ammonium will noticeably affect release.

Some ionic small molecule drugs such as lumefantrine (for structure, see Table 3) are already hydrophobic, so it is not possible to form an aqueous solution as the starting point for HIP. Hydrophobic ion pairing an already-hydrophobic drug can be useful – for example, to decrease drug crystallinity^{30,46,47} – but the complex formation is more challenging. Lumefantrine's tertiary amine has a pK_a of 8.7, but the drug's $\log P$ of 9.2 severely limits its ability to dissolve, and the amine to become charged, in water.⁴⁸ Dissolving lumefantrine free base in a nonpolar solvent such as tetrahydrofuran guarantees dissolution, but the extent of the amine's charge is more difficult to control and measure in a non-aqueous environment. As mentioned above, conversion to a salt form before complexation may be useful (Table 4).

Peptides. Many antibiotic peptides such as nisin and colistin (for structure, see Table 3) are cationic and strongly water soluble, with $\log P$ values less than 0. Basic amino acid residues in the peptide (lysine, histidine, arginine) are positively charged at physiological or acidic pH and are sites for ion pairing. Some cationic peptide drugs are manufactured as sulfate salts that



Table 1 Example anionic counterions used in hydrophobic ion pairing

Name	Structure	MW, Da	pK _a	log <i>P</i>	Used to pair with
1-Hydroxy-2-naphthoic acid (xinafoic acid)		188.2	3.02	2.6	AZD2811 (ref. 38 and 89)
2-Naphthalene sulfonic acid (NSA)		208.2	−1.8	2.14	Atazanavir ²⁸
Brilliant blue FCF		792.8	5.83 and 6.58	−1.45	Atenolol ¹⁵⁵
Carboxy methyl polyethylene glycol (CM-PEG)		PEG length not given			Bovine serum albumin ⁵⁶ Lysozyme ⁵⁶ r-met-HuGdNF ⁵⁶
Cholesteryl hemisuccinate		486.7	5.8	8.5	Colistin ¹⁵⁶ Doxorubicin ¹¹²
Cholic acid (sodium cholate)		408.6	4.98	2.02	AZD2811 (ref. 38 and 89) Bovine serum albumin ⁵⁶ Lysozyme ⁵⁶ r-met-HuGdNF ⁵⁶ Insulin ¹⁵⁷
Decanoic acid (sodium decanoate/sodium caprate)		194.3	4.9	4.09	Octreotide ^{9,96}
Dimyristoyl phosphatidyl glycerol (DMPG)		666.9	1.89	9.2	Insulin ⁴² Salmon calcitonin ⁸⁵
Dioleoyl phosphatidic acid (DOPA)		701	1.3	13.2	Doxorubicin ⁷¹ Gefitinib ³⁰
Docosahexaenoic acid		328.5	4.89	6.75	Doxorubicin ⁷⁰
Hexadecylphosphate		320.4		6.38	Doxorubicin ¹⁵⁸ Thymopentin ¹⁵⁹ Tobramycin ¹⁶⁰
Linoleic acid		280.5	4.77	6.8	Vancomycin ⁶⁴
N,N-Dipalmitoyl-L-lysine					Colistin ¹⁵⁶



Table 1 (Contd.)

Name	Structure	MW, Da	pK _a	log P	Used to pair with
Oleic acid (sodium oleate also used)		282.5	5	6.78	AZD2811 (ref. 38 and 89) Berberine ¹⁶¹ Desmopressin ^{77,86} Dorzolamide ⁸¹ Doxorubicin ^{106,121} Insulin ^{86,102,162} Leuprolide ^{86,94,101} Lumefantrine ⁴⁸ Lycobetaine ¹⁶³ Lysozyme ^{57,58} Octreotide ⁹⁶ OZ439 (ref. 43 and 154) Polymyxin B ⁷⁸ Salmon calcitonin ⁸⁵ Vincristine ¹⁶⁴
Pamoic acid (disodium pamoate also used)		388.4	2.68	6.17	AZD2811 (ref. 38) Bovine serum albumin ¹⁶⁵ Cinnarizine ⁴⁷ Clozapine ⁴⁷ Donepezil ¹⁶⁶ Insulin ¹⁶⁵ Leuprolide ¹⁶⁵ Polymyxin B ⁷⁸ Doxorubicin ⁶¹ Propanolol ⁶¹ Quinidine sulfate ⁶¹ Verapamil ⁶¹
Sodium acetate		82	4.7	−0.2	
Sodium cholesteryl sulfate		466.3	3.13	4.2	Colistin ¹⁵⁶
Sodium decanesulfonate (SDS)		244.3		3.75	Doxorubicin ¹¹⁶
Sodium deoxycholate		392.6	4.65	3.8	AZD2811 (ref. 38) Bovine serum albumin ¹⁶⁵ Ciprofloxacin ⁸⁸ Insulin ^{80,93,165} Lanreotide ⁹⁸ Leuprolide ¹⁶⁵ Mitoxantrone diHCl ⁷⁹ Octreotide ^{9,96} Papain ⁹⁷ Salmon calcitonin ⁸⁵ α-Chymotrypsin ¹⁶⁷ Atazanavir ²⁸ AZD2811 (ref. 38 and 89) Bevacizumab ¹⁶⁸ Bovine serum albumin ^{56,169} Cisplatin ⁸³ Concanavalin A ¹⁶⁷ Desmopressin ^{45,77,86,170} Doxorubicin ¹¹⁶ Gentamycin ^{82,117–119,171} Irinotecan ²⁹ Lanreotide ⁹⁸ Leuprolide ^{45,84,86,110,172} Lysozyme ⁵⁶ Minocycline ¹⁷³
Sodium docusate (AOT, sodium dioctyl sulfosuccinic acid, sodium bis-2-ethylhexyl-sulfosuccinate)		444.6	−0.75	5.2	



Table 1 (Contd.)

Name	Structure	MW, Da	pK _a	log P	Used to pair with
Sodium dodecyl benzenesulfonate (SDBS)		348.5	−1.7	3.73	Mtb8.4 (ref. 174) Naloxone ¹¹⁷ Naltrexone ¹¹⁷ Octreotide ⁹ r-met-HuGdNF ⁵⁶ Tobramycin ¹⁷⁵ Trypsin ¹⁶⁷ Vancomycin ¹⁷⁶
Sodium dodecyl sulfate (sodium lauryl sulfate)		288.4	−1.5	1.6	Bovine serum albumin ⁵⁶ Desmopressin ^{77,86} Dorzolamide ⁸¹ IGG-Fab fragment ⁹⁰ Insulin ^{49,58,84,86,111,177,178} Irinotecan ²⁹ Leuprolide ^{11,84,86} Lysozyme ^{18,56,57} Melittin ¹⁰⁹ Octreotide ^{92,96} Polymyxin B ⁷⁸ r-met-HuGdNF ⁵⁶
Sodium laurate (sodium dodecanoate)		222.3	4.95	5.3	Bovine serum albumin ¹⁶⁵ Insulin ¹⁶⁵ Leuprolide ¹⁶⁵
Sodium n-octadecyl sulfate (sodium stearyl sulfate)		372.5		6.8	Desmopressin ⁷⁷ Lanreotide ⁹⁸
Sodium stearate (stearic acid also used)		306.5	4.7	8.23	Desmopressin ⁷⁷ Doxorubicin ⁶¹ Propanolol ⁶¹ Quinidine sulfate ⁶¹ Verapamil ⁶¹
Sodium stearyl glutamate (SSG)		435.6		6.3	Bovine serum albumin ¹⁶⁵ Insulin ¹⁶⁵ Leuprolide ¹⁶⁵
Sodium taurodeoxycholate (STDC)		499.7	−0.94	4.5	Doxorubicin ^{72,95,116} Idarubicin ⁹⁵
Sodium tetradecyl sulfate		316.4	−1.1	5.04	Doxorubicin ⁹⁵ Idarubicin ⁹⁵
Sodium tripolyphosphate		367.9	0.89	−1.9	Irinotecan ²⁹



Table 1 (Contd.)

Name	Structure	MW, Da	pK _a	log P	Used to pair with
Taurocholic acid (sodium taurocholate also used)		515.7	1.4	0.79	Bovine serum albumin ⁵⁶ Lanreotide ⁹⁸ Lysozyme ⁵⁶ r-met-HuGdNF ⁵⁶ IGG-Fab fragment ⁹⁰
Vitamin E (α -tocopherol) succinate		530.8	4	10.2	Doxorubicin ¹⁰⁵

dissociate readily in water and do not have the same solubility and ionization challenges as hydrophobic small molecules. For peptides with only cationic charges such as polymyxin B, aqueous complexation with anionic surfactants is straightforward. Zwitterionic peptides are more challenging, however. If a peptide contains both cationic and anionic groups, it is possible that complexing only the cationic sites and leaving anionic sites charged and exposed (or *vice versa*) will impart sufficient hydrophobicity for the desired application. This is especially true when one kind of charged site significantly outnumbers the other, as in the case of a COOH-terminated peptide with five cationic sites. Complexing five out of the six charged sites with hydrophobic counterions may reduce water solubility enough to enable encapsulation.

When there are approximately the same number of cationic and anionic sites on a zwitterionic peptide, though, complexing only one charge may not be sufficient. It is preferable to use only one counterion species to complex a molecule, rather than adding both anionic and cationic hydrophobic counterions (which will invariably pair with each other and precipitate, complicating stoichiometry and adding difficult-to-separate insoluble salts to the system) in an attempt to complex every charged site. In this case, shifting the pH to turn off one type of charge is a valid approach. Consider insulin, a 5.8 kDa peptide with 51 residues, 6 of which are cationic and 6 anionic. Insulin has no net charge at its isoelectric point at pH 5.3. Researchers have reported shifting the solution pH either up or down from 5.3 to deprotonate insulin's basic residues or protonate its acidic residues, respectively.^{42,49–53} With only one type of charge, the peptide can then be hydrophobically ion paired (Fig. 3).

Researchers should consider several factors when using a pH shifting strategy. First, peptides are subject to degradation under basic conditions, so shifting the pH to strongly acidic is likely preferable.⁵⁴ Second, the complexing counterions are subject to protonation or deprotonation under extreme pH conditions as well. Insulin has only cationic charges at pH 1.5, but an anionic fatty acid counterion such as oleic acid (pK_a ~ 5) will be protonated under those conditions too. A much more acidic counterion such as sodium dodecyl sulfate (pK_a ~ 1.5) or sodium docusate (pK_a ~ 0.75) must be used. These sulfate surfactants are less biocompatible than fatty acids, in part because of this difference in pK_a. The same considerations

apply when shifting the pH to basic. Quaternary amines may be the only groups to reliably retain their cationic charge at a high pH, but using these cytotoxic surfactants to complex an anionic peptide presents its own challenges.

Proteins. Protein therapeutics are commonly zwitterionic, and all the considerations of net charge, ratio of basic to acidic residues, pI, and pH shifting that apply to zwitterionic peptides also apply to proteins. An additional complication when complexing proteins is their sensitivity to denaturation. Some surfactants such as sodium dodecyl sulfate disrupt tertiary structure and cause proteins to denature.⁵⁵ Using 'gentler' surfactants such as fatty acids may cause less degradation, but might also prevent the pH shifting approaches discussed above.

A popular model protein for hydrophobic ion pairing and encapsulation is lysozyme, which is cationic at physiological pH.^{18,56–59} Lysozyme's enzymatic activity can be easily measured *via* a cell lysis assay; therefore, testing whether or not the protein was denatured during complexation, encapsulation, and release is straightforward. Devrim *et al.* found that even when using sodium dodecyl sulfate as an ion pairing agent, released lysozyme retained over 80% of its enzymatic activity.¹⁸ Yoo *et al.* reported that the enzyme was more stable in DMSO when ion paired using SDS or oleate, and postulated that HIP complexation could help stabilize a protein's tertiary structure.⁵⁷ Notably, lysozyme tends to refold into its native active form, so not all techniques that claim to 'retain' the protein's activity will do so for all enzymes.

2.3 Key parameters for hydrophobic ion pairing

The following section is intended to guide the reader in choosing an effective hydrophobic counterion for a given encapsulation and/or delivery system. It is important to note that the goals for a given delivery system – *e.g.* drug chemistry, drug loading, encapsulation technique, biological target, release profile, *etc.* – are the most important factors when choosing a suitable counterion. This section will overview how parameters such as drug : counterion charge ratio and counterion chemistry affect those goals.

Counterion chemistry: hydrophobicity. The log *P*, the logarithm of the octanol–water partition coefficient, is a typical measure of hydrophobicity that is convenient for HIP. For



Table 2 Example cationic counterions used in hydrophobic ion pairing

Name	Structure	Mol. wt.	pK _a	log P	Paired with
Arginine-hexadecanoyl ester (AHE)		398.6		0.19	Daptomycin ⁴¹ Heparin ⁴¹
Arginine-nonyl ester (ANE)		300.5		−0.06	Daptomycin ⁴¹ Heparin ⁴¹
Benethamine(<i>N</i> -benzyl-2-phenylethanamine)		211.3		3.6	Retinoic acid ^{65,108,115}
Chitosan		Varies			Insulin ⁵³
Dodecylamine (laurylamine)		185.3	10.6	5.2	Retinoic acid ^{146,107,114}
Hexadecyl trimethylammonium(cetrimonium) bromide (CTAB)		364.5	—	2.69	Ovalbumin ³⁹ Pemetrexed ¹⁰³ Poly(I:C) ³⁹
Maprotiline		277.4	10.5	5.1	Retinoic acid ¹¹⁵
<i>N</i> ^α -Deoxychoyl-L-lysyl-methylester		534.8		3.8	Pemetrexed ⁴
<i>N,N'</i> -Dibenzyl ethylenediamine(benzathine)		240.3		2.86	α-Lipoic acid ⁴⁷
<i>N,N</i> -Dimethyl dodecylamine (DDA)		213.4	9.97	5.91	Am80 (ref. 40)
<i>N,N</i> -Dimethyl hexylamine		129.2	10.4	2.72	Am80 (ref. 40)
<i>N,N</i> -Dimethyl octadecylamine(dimethyl stearamine)		297.6		8.8	Am80 (ref. 40)
Stearylamine(octadecylamine)		269.5	10.7	7.7	Retinoic acid ^{146,65,107,114}
Tetrabutyl ammonium bromide (TBAB)		322.4	—	2.1	Bromothymol blue ⁶⁶ Rose bengal ⁶⁶
Tetraheptyl ammonium bromide (THA)		490.7	—	8.16	Isoniazid methanesulfonate ¹⁷⁹
Tetrahexyl ammonium bromide		434.6	—	6.16	Bromothymol blue ⁶⁶ Rose bengal ⁶⁶



Table 2 (Contd.)

Name	Structure	Mol. wt.	pK _a	log P	Paired with
Tetraoctyl ammonium bromide (TOAB)		546.7	—	9.16	Bromothymol blue ⁶⁶ Rose bengal ⁶⁶
Tetrapentyl ammonium bromide (TPA)		378.5	—	4.14	Isoniazid methanesulfonate ¹⁷⁹
Triethylamine (TEA)		101.2	10.8	1.65	Retinoic acid ^{146,65,107,114}

a given charged head group, the longer or more saturated an alkyl tail, or the more alkyl tails, the higher the log *P*. Stearic acid (lipid number 18 : 0), for example, has a higher log *P* than both capric acid (lipid number 10 : 0) and oleic acid (lipid number 18 : 1). Quaternary amines also follow this trend, though their alkyl tails are fully saturated. Dimethyl dihexadecyl ammonium bromide (two methyl tails and two C₁₆ tails) is more hydrophobic than CTAB (three methyl tails and one C₁₆ tail), and tetraheptyl ammonium bromide (four C₇ tails) is more hydrophobic than tetrabutyl ammonium bromide (four C₄ tails). Note that log *P* values for a free acid/base or an ionized surfactant may be different when reported from measurements or calculations. In general, the higher the log *P* of the counterion used, the higher the log *P* of the resulting complex.^{40,60}

The most hydrophobic counterion is not always the best to use. Increasing alkyl tail length or number of tails increases molecular weight, meaning the final complex will have a lower mass fraction of drug. This drives down drug loading in a delivery vehicle, all else (charge ratio, encapsulation efficiency, *etc.*) being equal. Availability and cost are another factor, since not all fatty acids or quaternary amines are commercially available at high purity and low cost. Solubility limitations are discussed in the following paragraph. Finally, comparing log *P* values among fatty acids is straightforward, but it is difficult *a priori* to compare the effect of a fatty acid *vs.* a bile acid or other carboxylic acid surfactant (*e.g.* oleic acid *vs.* pamoic acid, which is divalent) on complexation.

Extremely hydrophobic counterions, particularly those with protonated (free acid) carboxylic head groups, are difficult to dissolve in water for ion pairing. For the pairing to be effective, care should be taken to ensure that both species are dissolved and ionized prior to complexation. We recommend using a counterion's most water-soluble salt form, usually a sodium salt for anions and a bromide salt for cations.⁶¹ For example, oleic acid is sparingly soluble in water, but sodium oleate is water-soluble up to 10 wt%.^{62,63}

When choosing among different counterions with various log *P* values, it is important to keep in mind why HIP is needed. This will vary by the encapsulation technique used. For example, when using nanoprecipitation, the primary goal of

complexation is to *decrease water solubility*. When using an emulsion or SLN approach, however, the main goal is to *increase lipophilicity*. These distinctions will be discussed in further detail in Section 3, which focuses on encapsulation strategies, but we will give a brief example here. Consider vancomycin, a 1450 Da peptide with a single ionisable primary amine. We have found that vancomycin cannot be made to precipitate in Flash NanoPrecipitation, even using HIP, due to its low charge density. Kalhapure *et al.*, however, improved vancomycin encapsulation efficiency from 16.8% to and 70.7% by pre-forming a vancomycin : linoleic acid complex prior to formulation by hot homogenization and ultrasonication using the solid lipid Compritol 888 ATO and additional surfactants.⁶⁴ It is likely that vancomycin's increased lipophilicity, rather than improved hydrophobicity, led to this result. Adding oleate's 18-carbon tail to vancomycin likely improved the API's ability to interact with and remain associated with Compritol 888's alkyl tail.

A counterion's log *P* value is therefore not the only factor to consider when considering hydrophobicity.⁵⁶ It is important to remember that in addition to excluding water, hydrophobic domains on a counterion can interact hydrophobically and sterically with (1) one another, (2) hydrophobic domains on the complexed drug, and (3) the delivery vehicle's polymers, lipids, or surfactants.^{65,66} Hydrophobic interactions may make a counterion with aromatic groups more suitable for use than one with an aliphatic tail, for example, or give rise to favourable cooperativity between a drug and counterion with an unsaturated aliphatic tail, even though one with a saturated tail may have a higher log *P*. These interactions remain an active area of research.

Counterion chemistry: pK_a and pH. Counterions must be charged to ionically complex. Sulfate and sulfonate anions and quaternary amine cations are essentially always charged in aqueous environments, but the degree of ionization for carboxylic acids and primary, secondary, and tertiary amines varies with pH. Therefore pH and pK_a (of the drug molecule and the counterion) are both important to consider during HIP. Operating at a pH near one species' pK_a value is not advised, because charge ratios are difficult to predict and control



Table 3 Examples of hydrophobic ion pairing, sorted by therapeutic

Name	Structure/etc.	Paired with	Formulation technique
α -Chymotrypsin	25 kDa protein, 241 residues, pI: 8.75	Sodium docusate ¹⁶⁷	Solvent evaporation with polymethyl methacrylate, polystyrene, or poly(vinyl acetate) ¹⁶⁷
α -Lipoic acid		<i>N,N'</i> -Dibenzylethylene diamine (DBDA), ⁴⁷ note: included pamoic acid to frustrate α LA : DBDA recrystallization and improve encapsulation	PLA- <i>b</i> -PEG NPs by Flash NanoPrecipitation, <i>in situ</i> HIP ⁴⁷
Am80		<i>N,N</i> -Dimethyldodecyl amine (DDA) ⁴⁰ <i>N,N</i> -Dimethylhexyl amine ⁴⁰ <i>N,N</i> -Dimethyloctadecyl amine ⁴⁰	Block copolymer micelles by evaporation-sonication ⁴⁰
Atazanavir		2-Naphthalene sulfonic acid ²⁸ Sodium docusate (AOT) ²⁸	SEDDS ²⁸
Atenolol		Brilliant blue FCF ¹⁵⁵	PLGA NPs by nanoprecipitation ¹⁵⁵
AZD2811		Oleic acid ^{38,89} 1-Hydroxy-2-naphthoic acid ^{38,89} Cholic acid ^{38,89} Sodium deoxycholate ³⁸ Docusate sodium ^{38,89} Pamoic acid ³⁸	Oil in water (o/w) nanoemulsification solvent extraction to form PLA-PEG NPs using <i>in situ</i> HIP ^{38,89}
Berberine		Oleic acid ¹⁶¹	Liquid crystalline nanoparticulates by a hydrotrope method ¹⁶¹
Bevacizumab	149 kDa antibody	Docusate sodium ¹⁶⁸	Lipid coacervation ¹⁶⁸
Bovine serum albumin (BSA)	66.5 kDa protein, 583 residues, pI: 4.7	Cholic acid ⁵⁶ CM-PEG ⁵⁶ Sodium dodecyl sulfate ⁵⁶ Taurocholic acid ⁵⁶ Sodium docusate ⁵⁶	Double emulsion ⁵⁶ Single emulsion ⁵⁶
Bromothymol blue		Dextran sulfate ⁹¹ Sodium deoxycholate ¹⁶⁵ Sodium laurate ¹⁶⁵ Sodium stearyl glutamate ¹⁶⁵ Pamoic acid disodium ¹⁶⁵ Tetrabutylammonium bromide ⁶⁶ Tetrahexylammonium bromide ⁶⁶ Tetraoctylammonium bromide ⁶⁶	Double emulsion ⁵⁶ Single emulsion ⁵⁶ SEDDS ¹⁶⁹ Solid in oil in water (S/O/W) to form PLGA NPs ⁹¹ SEDDS ¹⁶⁵
Chlorhexidine		Losartan ¹⁵²	Nanoprecipitation ¹⁵²
Cinnarizine		Pamoic acid, ⁴⁷ note: Also unsuccessfully tried camphor-10 sulfonic acid (micellized), cinnamic acid, palmitic acid, and oleic acid	PLA- <i>b</i> -PEG NPs by Flash NanoPrecipitation, <i>in situ</i> HIP ⁴⁷



Table 3 (Contd.)

Name	Structure/etc.	Paired with	Formulation technique
Ciprofloxacin		Sodium deoxycholate ⁸⁸	Oil-in-water (o/w) submicron emulsion ⁸⁸
Cisplatin		Sodium docusate ⁸³	Stearic acid coacervation ⁸³
Clozapine		Pamoic acid ⁴⁷	PLA- <i>b</i> -PEG NPs by Flash NanoPrecipitation, <i>in situ</i> HIP ⁴⁷
Colistin		Cholesteryl hemisuccinate ¹⁵⁶ <i>N,N</i> -Dipalmitoyl-L-lysine ¹⁵⁶ Sodium cholesteryl sulfate ¹⁵⁶	PLA NPs by emulsion evaporation ¹⁵⁶
Concanavalin A	104–112 kDa protein (tetramer), pI: 4.5–5.5	Sodium docusate ¹⁶⁷	Solvent evaporation with polymethyl methacrylate, polystyrene, or poly(vinyl acetate) ¹⁶⁷
Dalargin		Dextran sulfate ¹⁰⁴	PLGA-PEG NPs by S/O/W emulsion ¹⁰⁴
Daptomycin		Arginine-hexadecanoyl ester ⁴¹ Arginine-nonyl ester ⁴¹	N/A; proof-of-concept HIP using novel cationic surfactants demonstrates precipitation and increased log <i>P</i> ⁴¹
Desmopressin		Oleic acid ⁷⁷ Sodium docusate ^{45,77,86,170} Sodium dodecyl sulfate ^{77,86} Sodium stearate ⁷⁷ (note: less effective than SDS, SEDDS ^{45,77,86,170} AOT, and oleate) Sodium stearyl sulfate ⁷⁷ (note: less effective than SDS, AOT, and oleate)	
Dexamethasone valine valine prodrug		Dextran sulfate ¹²⁰	PLGA NPs by S/O/W emulsion ¹²⁰
Donepezil		Pamoic acid ¹⁶⁶	High pressure homogenization with D- α -tocopherol polyethylene glycol 1000 succinate ¹⁶⁶
Dorzolamide		Oleic acid ⁸¹ Sodium dodecyl sulfate ⁸¹	PLGA NPs or PEG3-PSA microparticles by S/O/W emulsion ⁸¹
Doxorubicin		Alginate acid ⁶¹ Cholesteryl hemisuccinate ¹¹² Dextran sulfate ^{61,95} Dioleoyl phosphatidic acid (DOPA) ⁷¹ Docosahexaenoic acid ⁷⁰ Hexadecylphosphate ¹⁵⁸ Hyaluronic acid ¹⁵³	Microemulsion by stearic acid coacervation ⁶¹ Thin film dispersion ¹¹² Microemulsion by stearic acid coacervation ⁶¹ Warm wax microemulsion solvent evaporation ⁹⁵ PLA- <i>b</i> -PEG NPs by nanoprecipitation ⁷¹ SLNs by hot melt ultrasound emulsification ⁷⁰ SLNs by warm oil-in-water microemulsion with stearic acid and taurocholate sodium ¹⁵⁸ Thin film dispersion by lipid film hydration with suspended HIP complex and homogenization ¹⁵³



Table 3 (Contd.)

Name	Structure/etc.	Paired with	Formulation technique
Gefitinib		Oleic acid ^{106,121}	70 °C high-pressure homogenization ¹²¹ High-pressure film homogenization ¹⁰⁶
		Sodium acetate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹
		Sodium alginate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹
		Sodium decanesulfonate ¹¹⁶	Microemulsion by stearic acid coacervation ¹¹⁶
		Sodium docusate ¹¹⁶	Microemulsion by stearic acid coacervation ¹¹⁶
		Sodium stearate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹
		Sodium taurodeoxycholate ^{72,95,116}	Warm wax microemulsion solvent evaporation ⁹⁵ Microemulsion by stearic acid coacervation ¹¹⁶
		Sodium tetradecyl sulfate ⁹⁵	Microemulsion by shear and ultrasonic homogenization after drying from molten stearyl alcohol ⁷²
		Vitamin E succinate ¹⁰⁵	Warm wax microemulsion solvent evaporation ⁹⁵ SLNs by hot melt ultrasound emulsification ¹⁰⁵
		Dioleoyl phosphatidic acid (DOPA) ³⁰	Nanoprecipitation with doxorubicin-conjugated PLA- <i>b</i> -PEG NPs ³⁰
Gentamicin		Sodium docusate ^{82,117–119,171}	PLA microparticles by precipitation with compressed antisolvent ^{117,171} Microparticles by PCA using stabilizer poly(methyl vinyl ether- <i>co</i> -maleic anhydride) ¹¹⁸ PCA with no stabilizer ^{82,119} PLGA NPs by emulsion solvent evaporation ^{82,119}
		Arginine-hexadecanoyl ester ⁴¹ Arginine-nonyl ester ⁴¹	N/A; proof-of-concept HIP using novel cationic surfactants demonstrates precipitation and increased log <i>P</i> ⁴¹
Heparin		Dextran sulfate ⁹⁵ Sodium taurodeoxycholate ⁹⁵ Sodium tetradecyl sulfate ⁹⁵	Warm wax microemulsion solvent evaporation ⁹⁵
Idarubicin			
IGG-Fab fragment 48 kDa protein		Sodium dodecyl sulfate ⁹⁰ Taurocholic acid ⁹⁰ Dextran sulfate ⁹⁰	Modified nanoprecipitation ⁹⁰ S/O/W PLGA NPs ⁹⁰
Insulin	5.8 kDa peptide, 51 residues (6 cationic and 6 anionic), pI: 5.3	Cholic acid ¹⁵⁷	Reverse micelle-double emulsion using palmitic and stearic acid ¹⁵⁷
		Chitosan ⁵³	Homogenization and stabilization with SDS ⁵³
		Dimyristoyl phosphatidyl glycerol ⁴²	SNEDDS ⁴²
		Oleic acid ^{58,102,162}	S/O/W emulsion ⁵⁸ PLGA NPs by emulsion solvent diffusion ^{102,162} SEDDS ¹⁶⁵
		Pamoic acid disodium ¹⁶⁵	
		Sodium laurate ¹⁶⁵	
		Sodium stearoyl glutamate ¹⁶⁵	
		Sodium deoxycholate ^{80,93,165}	PLGA NPs by emulsion solvent diffusion ⁹³ S/O/W emulsion ⁸⁰ SEDDS ¹⁶⁵ SEDDS ⁸⁶
		Sodium docusate ^{84,86}	Stearic acid coacervation ⁸⁴ Stearic acid coacervation ⁸⁴
		Sodium dodecyl sulfate ^{49,84,111,177,178}	PLGA NPs by emulsion solvent diffusion ^{111,177,178} Electrospray with stearic or pamoic acid ⁴⁹
Irinotecan		Sodium docusate ²⁹ Sodium dodecyl sulfate ²⁹ Sodium tripolyphosphate ²⁹	PEG- <i>b</i> -PLGA NPs via water/oil/water double emulsion; <i>in situ</i> HIP ²⁹
		Tetraheptylammonium bromide ¹⁷⁹	Precipitation with compressed antisolvent (PCA) ¹⁷⁹




Table 3 (Contd.)

Name	Structure/etc.	Paired with	Formulation technique
Isoniazid methanesulfonate		Tetrapentylammonium bromide ¹⁷⁹	
Lanreotide		Sodium deoxycholate ⁹⁸ Sodium docusate ⁹⁸ Sodium stearyl sulfate ⁹⁸ Taurocholic acid ⁹⁸	SNEDS ⁹⁸
Leuprolide		Oleic acid ^{94,101} Sodium deoxycholate ¹⁶⁵ Sodium laurate ¹⁶⁵ Sodium stearyl glutamate ¹⁶⁵ Pamoic acid disodium ¹⁶⁵ Sodium docusate ^{45,84,86,172}	PLGA microspheres by O/W emulsion ¹⁰¹ SMEDDS ⁹⁴ SEDSS ¹⁶⁵
Loperamide		Sodium dodecyl sulfate ^{11,84} Sodium stearate ⁸⁷	SEDSS ^{45,86} Stearic acid coacervation ⁸⁴ Oligosaccharide ester microparticles by spray drying ¹⁷² Solid lipid nanoparticles and nanostructured lipid carriers by high pressure homogenization ¹¹⁰ Stearic acid coacervation ⁸⁴ Hydrogen bonding complexation between polyacrylic acid and Pluronic F68 (ref. 11) Solid lipid NPs by: solvent diffusion ⁸⁷ Oil-in-oil (O/O) emulsion-evaporation ⁸⁷
Losartan		Dextran sulfate ¹⁰⁴	PLGA-PEG NPs by S/O/W emulsion ¹⁰⁴
Lumefantrine		Chlorhexidine ¹⁵²	Nanoprecipitation ¹⁵²
Lycobetaine		Oleic acid ⁴⁸	SEDSS ⁴⁸
Lysozyme	14.4 kDa protein, 129 residues, pI: 11.35	Oleic acid ¹⁶³	Emulsion by lipid film hydration high-pressure homogenization ¹⁶³
Melittin	2.8 kDa peptide, 26 residues, pI: 12.01	Cholic acid ⁵⁶ CM-PEG ⁵⁶ Dextran sulfate ⁵⁹ Oleic acid ^{57,58} Sodium docusate ⁵⁶ Sodium dodecyl sulfate ^{18,57} Taurocholic acid ⁵⁶	Double emulsion ⁵⁶ Single emulsion ⁵⁶ Double emulsion ⁵⁶ Single emulsion ⁵⁶ Emulsion solvent diffusion ⁵⁹ PLGA NPs by emulsion diffusion ⁵⁷ S/O/W emulsion ⁵⁸ Double emulsion ⁵⁶ Single emulsion ⁵⁶ PLGA NPs by emulsion diffusion ⁵⁷ S/O/W emulsion: Polymer/lipid NPs ¹⁸ Double emulsion ⁵⁶ Single emulsion ⁵⁶
Minocycline		Sodium dodecyl sulfate ¹⁰⁹	PLGA nanoparticles by emulsion solvent diffusion ¹⁰⁹
		Sodium docusate ¹⁷³	PLGA NPs by emulsion-solvent-diffusion ¹⁷³



Table 3 (Contd.)

Name	Structure/etc.	Paired with	Formulation technique
Mitoxantrone dihydrochloride		Sodium deoxycholate ⁷⁹	Nanoprecipitation ⁷⁹
Mtb8.4	Protein, TB antigen, pI: 6.3	Sodium docusate ¹⁷⁴	PLG microspheres by emulsification ¹⁷⁴
Naloxone		Sodium docusate ¹¹⁷	PLA microparticles by precipitation with compressed antisolvent ¹¹⁷
Naltrexone		Sodium docusate ¹¹⁷	PLA microparticles by precipitation with compressed antisolvent ¹¹⁷
Octreotide		Dextran sulfate ⁹² Oleic acid ⁹⁶ Sodium decanoate ^{9,96} Sodium deoxycholate ^{9,96} Sodium docusate ⁹ Sodium dodecyl sulfate ^{92,96}	S/O/W emulsion ⁹² SNEDDS ⁹⁶ SNEDDS ⁹⁶ SEDDS ⁹ SNEDDS ⁹⁶ SEDDS ⁹ SEDDS ⁹ S/O/W emulsion ⁹² SNEDDS ⁹⁶
Ovalbumin (OVA)	43 kDa protein, 385 residues, pI: 5.19	Cetrimonium bromide (CTAB) ³⁹	pH-sensitive polyketal microparticles by single emulsion ³⁹
OZ439 mesylate (artefenomel)		Sodium oleate ^{43,154}	HPMCAS NPs by Flash NanoPrecipitation; <i>in situ</i> HIP ^{43,154}
Papain	23.4 kDa protein, 212 residues, pI: 8.8–9.6	Sodium deoxycholate ⁹⁷	SEDDS ⁹⁷
Pemetrexed		Cetrimonium bromide (CTAB) ¹⁰³ <i>N</i> ^α -Deoxycholy-L-lysyl-methylester ⁴	Lyotropic liquid crystalline nanoparticles by homogenization (<i>in situ</i> HIP) ¹⁰³ W/O/W emulsion ⁴
Polymyxin B		Oleic acid sodium salt ⁷⁸ Pamoic acid sodium salt ⁷⁸ Sodium dodecyl sulfate ⁷⁸ Sodium dodecyl benzenesulfonate ⁷⁸	PCL- <i>b</i> -PEG NPs by Flash NanoPrecipitation (FNP), <i>in situ</i> HIP, ⁷⁸ note: sodium decanoate, myristate, deoxycholate, 2-naphthalenesulfonate, 1-heptanesulfonate, 1-octane-sulfonate, and 1-decanesulfonate formed a precipitate when mixed with polymyxin B at 1 : 1 charge ratio but did not form NPs by FNP. Sodium hexanoate, benzenesulfonic acid, camphorsulfonic acid, and 1,2-ethanesulfonate did not form a precipitate when mixed with polymyxin B at 1 : 1 charge ratio.
Poly(inosinic acid)-poly(cytidylic acid) (poly(I : C))	Double-stranded RNA analog, TLR3 agonist	Cetrimonium bromide (CTAB) ³⁹	pH-sensitive polyketal microparticles by single emulsion ³⁹
Propranolol		Alginate acid ⁶¹ Dextran sulfate ⁶¹ Sodium acetate ⁶¹ Sodium stearate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹



Table 3 (Contd.)





Name	Structure/etc.	Paired with	Formulation technique
Quinidine sulfate		Alginic acid ⁶¹ Dextran sulfate ⁶¹ Sodium acetate ⁶¹ Sodium stearate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹
r-met-HuGdNF	Recombinant methionyl human Glial-cell line derived neurotrophic factor	Cholic acid ⁵⁶ CM-PEG ⁵⁶ Sodium docusate ⁵⁶ Sodium dodecyl sulfate ⁵⁶ Taurocholic acid ⁵⁶ Benethamine ^{65,108,115} Laurylamine ^{46,107,114}	Double emulsion ⁵⁶ , single emulsion ⁵⁶
Retinoic acid		Maprotiline (both HCl and free base) ¹¹⁵ Stearylamine ^{46,65,107,114} Triethylamine ^{46,65,107,114}	Hot melt homogenization using ultrasound emulsification ^{41–43,65,108,115}
Rose bengal		Tetrabutylammonium bromide ⁶⁶ Tetrahexylammonium bromide ⁶⁶ Tetraoctylammonium bromide ⁶⁶	Encapsulated into polystyrene microparticles using compressed carbon dioxide to plasticize polystyrene MPs and allow diffusion in ⁶⁶
Salmon calcitonin	3.4 kDa peptide, 32 residues, pI: 8.86	Dimyristoyl phosphatidyl glycerol (DMPG) ⁸⁵ Oleic acid ⁸⁵ Sodium deoxycholate ⁸⁵	PLGA NPs by solvent diffusion ⁸⁵
Thymopentin		Hexadecylphosphate ¹⁵⁹	Warm oil in water microemulsion ¹⁵⁹
Tobramycin		Hexadecylphosphate ¹⁶⁰ Sodium docusate ¹⁷⁵	Warm oil in water microemulsion ¹⁶⁰ PLGA NPs by O/W emulsion ¹⁷⁵
Trypsin	23 kDa protein, 220 residues, pI: 10.1–10.5	Sodium docusate ¹⁶⁷ Linoleic acid ¹⁶⁴ Sodium docusate ¹⁷⁶	Solvent evaporation with polymethyl methacrylate, polystyrene, or poly(vinyl acetate) ¹⁶⁷ Hot homogenization and ultrasonication ⁶⁴ SEDDS ¹⁷⁶
Vancomycin			
Verapamil		Alginic acid ⁶¹ Dextran sulfate ⁶¹ Sodium acetate ⁶¹ Sodium stearate ⁶¹	Microemulsion by stearic acid coacervation ⁶¹
Vincristine		Oleic acid ¹⁶⁴	High pressure homogenization ¹⁶⁴

when one species is only partially ionized. Fig. 4 illustrates the pH window over which polymyxin B and oleic acid can be paired.

For peptide and protein drugs with many ionizable groups, the isoelectric point pI is a straightforward parameter to use, rather than trying to account for the pK_a and ionizable state of each charged residue. As in charged polymers, the curve of



Table 4 Examples of some polyvalent counterions used to encapsulate charged APIs. For a more complete survey of polyelectrolyte coacervation, see ref. 124–141

Name	Structure	MW, Da	pK _a	log P	Used to pair with:
Anions					
Alginate acid (sodium alginate also used)		Varies	1.5–3.5	–1.5	Doxorubicin ⁶¹ Propanolol ⁶¹ Quinidine sulfate ⁶¹ Verapamil ⁶¹ Bovine serum albumin ⁹¹ Dalargin ¹⁰⁴ Dexamethasone valine valine prodrug ¹²⁰ Doxorubicin ^{61,95} Idarubicin ⁹⁵ IGG-Fab fragment ⁹⁰ Loperamide ¹⁰⁴ Lysozyme ⁵⁹ Octreotide ⁹² Propanolol ⁶¹ Quinidine sulfate ⁶¹ Verapamil ⁶¹
Dextran sulfate		Varies	<2		
Hyaluronic acid		Varies	2.9	–8.2	Doxorubicin ¹⁵³
Cations					
Chitosan		Varies			Insulin ⁵³

charge *versus* pH for proteins is typically broader about the pI than an individual monomer would be. Curves denoting net charge *versus* pH are available for many proteins in the literature.^{67–69}

When either the drug or counterion used has a carboxylic acid or non-quaternary amine head group, the resulting complex may demonstrate pH-sensitive dissociation, which can be used to tune drug release. pH-dependent release is useful in drug delivery, for example, for targeting to endosomes or tumors. Cationic peptides are popular in the HIP literature; these are positively charged at physiological and acidic pHs, so pH-dependent release could be accomplished by pairing them with fatty acids, rather than sulfates or

phosphates. At a pH below the acid's pK_a, carboxylic acid become protonated, forming the uncharged free acid and decomplexing from their cationic counterparts. Hydrophobic and steric interactions from the former ion pair remain effective, but faster drug release can be expected.^{30,70–72} This will be discussed in more detail in the section on drug release.

Pinkerton *et al.* note that the pK_a values of the two charged species should be different by at least two pH units for an ion pair to reliably form. Importantly, the authors pointed out that solvent quality affects pK_a values. Therefore, when complexing in a mixed solvent of water and organics increasing the volume fraction of water may be useful to ensure complexation between



Fig. 3 Schematic illustrating the pH-shifting strategy using glycine as a model API. At low pH, carboxylic acid groups are protonated and uncharged. At high pH, amines are deprotonated and uncharged. For some zwitterionic APIs, researchers have reported shifting pH to one extreme to turn off one type of charge prior to ion pairing.





Fig. 4 An example species diagram showing the percent ionization of polymyxin B and oleic acid as a function of pH. From approximately pH 6.5 to 9, both species are nearly 100% ionized and could be paired with clear expectations about the resulting complex's charge ratio.

an anion and cation with pK_a values close to neutral.^{47,73,74} Other researchers have noted that physical confinement, *e.g.* in a delivery vehicle, may affect pK_a values as well; this phenomenon has the potential to affect HIP, and further study is needed.^{75,76}

An interesting study that to our knowledge has not been carried out in the literature would examine pH-sensitive ion paired drug release behavior as a function of counterion head group. For example, Zupancic *et al.* paired cationic desmopressin with both sodium *n*-octadecyl sulfate and sodium stearate.⁷⁷ The two have aliphatic tails of similar lengths, but the former has a sulfate head group and the latter has a carboxylic acid. If paired with a cationic API and encapsulated (*ceteris paribus*, and in a system with no other ionic or pH-sensitive components), we would expect the *n*-octadecyl sulfate system's release profile not to vary between pH values of *e.g.* 6.5, 4.5, and 2.5. The system containing stearate should release differently at the three pH values, since stearate's pK_a is 4.7. Zupancic *et al.* found that sodium docusate and sodium oleate complexed with and precipitated desmopressin more effectively than either stearate or *n*-octadecyl sulfate, so the latter two counterions were not examined further. Both counterions must effectively complex with and precipitate the drug of interest. It is possible that desmopressin (1.1 kDa, 1 cationic charge) has too low of a charge density for the experiment proposed above.

We have discussed counterion pK_a and $\log P$ values independently in the previous two sections. Researchers have noted that for a given counterion, it is prudent to also consider pK_a and $\log P$ together.^{56,65,78} Carneiro *et al.* noted that triethylamine was a worse hydrophobic counterion for pairing with all-trans retinoic acid than both benethamine and stearylamine. Although triethylamine is a stronger base than the other two counterions, and should therefore be able to interact more easily with retinoic acid, it is so much less hydrophobic that the resulting complex does not have the desired lipophilicity.⁶⁵ Likewise, Lu *et al.* screened fifteen counterions as candidates to form hydrophobic complexes with the pentacationic peptide polymyxin b.⁷⁸ We found that at constant counterion pK_a , the threshold $\log P$ required to form an ion pair hydrophobic

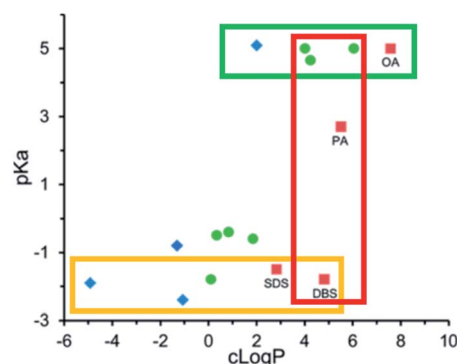


Fig. 5 pK_a and $\log P$ values for various anionic counterions. Complexes were pre-formed in MQ water at a 1 : 1 charge ratio with polymyxin b. Blue diamonds indicate no precipitate was observed; green circles indicate a precipitate was observed, but was insufficiently hydrophobic for nanoprecipitation; and red boxes indicate a sufficiently hydrophobic precipitate was formed. Adapted with permission from H. Lu, P. Rummaneeethorn, K. Ristoph, and R. K. Prud'homme, Hydrophobic Ion Pairing of Peptide Antibiotics for Processing into Controlled Release Nanocarrier Formulations, *Mol. Pharmaceutics*, 2018, 15(1), 216–225. Copyright (2017) American Chemical Society.⁷⁸

enough for their encapsulation method (nanoprecipitation) varied. For aliphatic fatty acid sodium salts such as sodium hexanoate, sodium decanoate, and sodium oleate, precipitates formed at counterion $\log P$ values above 4. Only sodium oleate, $\log P \sim 6.8$, formed complexes that precipitated as required for encapsulation (green box, Fig. 5). Sulfate surfactants formed sufficiently hydrophobic complexes at and above $\log P$ values of ~ 2 (yellow box, Fig. 5), suggesting that the sulfate surfactants interact more strongly with polymyxin b's cationic charges and form an ion pair more readily than the carboxylic acids. At a counterion $\log P$ of 5, dodecylbenzene sulfate formed a sufficiently hydrophobic complex, but fatty acids decanoate and myristate did not (red box, Fig. 5).

We recommend that researchers complex their drug of interest using a suite of counterions at first, noting the pK_a and $\log P$ values of the counterions used. The resulting complex's aqueous solubility and/or lipophilicity can be measured, and counterion chemistry or charge ratio can be varied to tune these values as desired.

Complexation: pre-formed vs. *in situ*. Ion paired complexes may be formed either prior to or during encapsulation; we call the former a 'pre-formed' complex and the latter an '*in situ*' complex. In the literature, the vast majority of complexes are pre-formed in water or a water–organic mixture, then isolated by precipitation or filtration, washed, and dried.^{39,49} This approach allows researchers to measure the complex's $\log P$ empirically and fully characterize it using techniques such as differential scanning calorimetry (DSC), X-ray diffraction (XRD), NMR, FTIR, *etc.*⁷⁹ Isolated complexes are often loaded into an oil phase or organic solvent (*e.g.* DCM^{80,81} or acetone⁸²) and treated as a lipophilic molecule. Since the oils and organics used are aprotic and often nonpolar, dissociation is unlikely.

Pre-formed complexes have a known stoichiometry and are already paired together, meaning electrostatic interactions between the drug and other delivery vehicle components are



Drug release as a function of drug : counterion charge ratio has also been reported.^{71,78,103} As may be expected, at charge ratios with more equivalents of counterion, the release rate of drug from delivery vehicle slows. This is likely because the complex is more hydrophobic, or slower to dissociate, or both. We will discuss this phenomenon in more detail in the following section.

A number of common encapsulation techniques have been applied to molecules during or after hydrophobic ion pairing. This section discusses specific considerations that should be made when using these techniques to encapsulate an ion paired molecule. A general overview of some processing parameters and important outcomes such as encapsulation efficiency and drug loading is provided.

Encapsulation efficiency (EE): the encapsulation efficiency for a given drug formulation is calculated by measuring the amount of free drug (*i.e.* not encapsulated in or associated with delivery vehicles) after complexation and encapsulation. Separating free drug from delivery vehicles may be done *via* ultrafiltration or centrifugation, when the free drug and delivery vehicles have very different sizes, or by a technique such as size exclusion chromatography, for separating proteins from nanoparticles where filtration is ineffective. Once the amount of free API is measured, encapsulation efficiency is reported according to the following equation:

For a formulation technique to be implemented at the industrial scale, high encapsulation efficiency – *i.e.* less material lost during processing – is desirable. High drug loading and few unit operations are also preferred.

Many papers report that HIP enabled researchers to encapsulate molecules that they previously could not, or that the technique improved their system's encapsulation efficiency, sometimes by more than 50%.^{18,49,84,87,88,90,101,104-110} Encapsulation efficiencies higher than 90%^{49,60,84,102,103,105,106,111} and as high as 100%^{57,78,82,109,112} have been reported.

$\log P$ measurements as a function of charge ratio are sometimes reported to go through a maximum around 1 : 1 as well.

strategies have inherent limits on drug loading; for example, S/O/W emulsions form percolation networks when the oil phase containing a hydrophobic drug reaches too high a volume fraction within a single droplet.¹² Therefore, in these systems there is an inverse relationship between drug loading and vehicle stability, which is undesirable at scale and for clinical application.

3.1 Emulsions

Single (e.g. oil-in-water, O/W)^{38,39,56} and double (e.g. solid-in-oil-in-water or water-in-oil-in-water, S/O/W or W/O/W),^{18,90,91} etc. – see Table 3 emulsions have been used to encapsulate ion paired complexes into droplets that may then be dried or otherwise further processed. Both require surfactants to stabilize, and typically a non-ionic species such as PVA is used. Using an ionic surfactant as an emulsion stabilizer may interfere with the hydrophobic complex's formation or stability.

Researchers commonly pre-form hydrophobic complexes prior to introducing them into an emulsified system. This has an advantage over *in situ* formation in that the complex may be added to the oil phase before emulsification, which promotes better encapsulation. If the hydrophilic component were introduced in the aqueous phase and the hydrophobic counterion were introduced *via* the oil phase, pairing would likely occur at oil-water interfaces if at all (and the degree of counterion ionization in the oil phase would be difficult to determine and control). If both components were added unpaired in a mixed oil phase, pairing would again be limited by ionization. Finally, if API and counterion were introduced in water and allowed to pair, the resulting hydrophobic complex would need to partition *into* the oil droplets, which would take longer and be less efficient than loading the pre-formed complex into oil, where it will prefer to remain.

A HIP complex's final geometry and possible amphiphilicity are another parameter that should be considered. A hydrophilic API's water-soluble charged group may be complexed by HIP, but other polar regions on the molecule may result in an amphiphilic complex that may tend to accumulate on the emulsion droplets' oil-water interface.⁹⁷ Using excess counterion, or a counterion with larger hydrophobic regions, may partially mitigate this effect. Proteins may be stabilized from denaturation at oil-water interfaces may be stabilized *via* ion pairing if they are complexed in such a way that their tertiary structure is largely preserved and their hydrophilic regions, which would lead to interfacial aggregation if exposed, are hidden.^{12,100}

3.2 Lipid nanoparticles

Hydrophobic complexes have been incorporated into solid lipid nanoparticles either by emulsification from a hot melt^{46,65,70,105,107,108,114,115} or by stearic acid coacervation.^{83,84,116} In the former, non-ionic lipids and surfactants such as glyceryl behenate were heated and added to an oil phase along with a pre-formed complex. The hot oily phase was added to water and sonicated. With no other charged species present, it is unlikely that the ion pair was disrupted prior to encapsulation. Carneiro *et al.* note that without complexation, the API of interest, all-trans retinoic acid, resides primarily at the lipid–

water interface, and that hydrophobic complexation helps incorporate it more fully in the lipid matrix.⁶⁵

Lipid nanoparticle formation by stearic acid coacervation involves lowering the pH of a solution of water and ethanol containing stearic acid to protonate and precipitate it as a free acid.^{83,84,116} In these systems, a pre-formed hydrophobic complex was added along with ethanol into the hot aqueous solution of stearic acid. Since ion pair formation and stability vary with ionic strength and pH, it remains unknown if the ion pair remained together during this formulation strategy, or if dissociation (and possibly re-pairing between the drug and stearic acid, before the pH dropped too low) occurred. Therefore the final stoichiometry and identity of the ion pair are difficult to know, even using a pre-formed system in the presence of additional potential ion pairing partners.

3.3 Precipitation

Controlled nanoprecipitation techniques such as Flash Nano-Precipitation take advantage of diffusion-limited aggregation between precipitating molecules in an aqueous or mixed solvent system. Hydrophobic complexes are well-suited for this approach, since their water solubility is very poor and they precipitate quickly. Rapid precipitation followed by stabilization, e.g. surface deposition of the hydrophobic block of a block copolymer, yields kinetically trapped core-shell nanoparticles.⁴⁷ Rapid, good mixing will result in homogeneous nucleation and growth, which is desirable in nanoprecipitation. Heterogeneous nucleation or poor mixing may allow sufficient time for the formation of a thermodynamically favoured micelle phase from excess hydrophobic counterion. This is undesirable because the hydrophobic polymers or polymer blocks used in nanoprecipitation may not deposit onto a micelle's charged surface as they would onto a hydrophobic surface, and the same kinetically-trapped particle may not be formed.

Researchers have demonstrated both *in situ* and pre-formed ion pairing approaches with nanoprecipitation. Water is typically used as an antisolvent to induce precipitation, so using salt forms of the API is a straightforward method of ensuring an initially ionized state of the API. This means that *in situ* complex formation, followed immediately by precipitation, is easy to accomplish. Unlike the water–oil systems such as those used for emulsions, nanoprecipitation systems use water-miscible organic solvents, meaning interfacial partitioning is not a factor. The main limit to complexation is therefore diffusion, falling in line with nanoprecipitation's typical diffusion-limited aggregation kinetics. Lu *et al.* reported that even in a Flash NanoPrecipitation system, where rapid mixing on the order of 2 ms is followed by nucleation, growth, and stabilization by block copolymer adsorption all within about 20 ms, complexes formed *in situ* were efficiently encapsulated.^{43,78} This suggests the time scale of complexation and precipitation is less than 20 ms. This is comparable to the precipitation time of a strongly hydrophobic (log *P* > 5) molecule – or pre-formed hydrophobic complex – in the same system.

Precipitation with a compressed antisolvent (PCA) has also been used to encapsulate HIP complexes into nanoparticles or microparticles.^{82,117–119} Because the mixing in PCA is between



a solvent containing the drug of interest and a chamber of pressurized gas, pre-formation of the hydrophobic complex is required.

3.4 Others

Other formulation strategies can be viewed through a similar lens to the one we have used above. Techniques that treat a pre-formed complex such as a typical hydrophobic molecule are valid provided they have not neglected the complex's sensitivity to salts and pH. For example, self (micro/nano)-emulsifying drug delivery systems (S[M/N]EDDS) may use either ionic or non-ionic surfactants. We described when discussing lipid nanoparticles that ionic surfactants could disrupt ion pairing or exchange with a complex's counterions – these considerations are important to keep in mind when modifying a system usually used to encapsulate a non-ionic hydrophobic molecule to one capable of encapsulating a HIP complex.

Systems that require pH modulation are not wholly ineligible for use with HIP, but care should be taken to ensure that the complex is not disrupted if possible. Consider Iqbal *et al.*, who used a unique method of interpolymer complexation between polyethylene glycol and poly(acrylic acid) to form nanoparticles.¹¹ This required adjusting the solution pH to 3 to protonate poly(acrylic acid); the cationic drug of interest was pre-formed with docusate and introduced along with Pluronic F68 in ethanol into an acidic aqueous PAA solution. Docusate has a sulfonate head group that should remain charged at pH 3, and PAA was already protonated and uncharged before the complex was added. Taken together, these suggest the pre-formed leuprolide:docusate complex was likely to survive intact in this formulation technique than in (1) one where it encountered another ionized species (as in the case of stearic acid coacervation discussed above) or (2) a system using a hydrophobic counterion (*e.g.* a fatty acid) that would be deprotonated at the final pH.

4. Ion paired drug release from a delivery vehicle

Drug release from a delivery vehicle containing a hydrophobic complex varies with the type of vehicle (core-shell nanoparticle, SLN, double emulsion, SEDDS, *etc.*), but useful similarities exist. The ion paired drug will behave like a hydrophobic molecule as long as it remains complexed. Once complexation is reversed, the original hydrophilic molecule and hydrophobic counterion are regenerated and will usually partition out of the delivery vehicle. De-complexation is driven by one of two main mechanisms: counterion competition by salts or pH-driven charge negation. The former occurs when salts in the surrounding medium are able to access the complex and outcompete the hydrophobic ion pair, leading to dissociation. The high ionic strength in the surrounding medium screens the charges between the two regenerated species, so re-complexation is unlikely. The former follows a similar mechanism, protonating or deprotonating one of the charged species and leading to de-complexation.

Both mechanisms depend on water accessing the hydrophobic complex. For this reason, the vehicle's type and

geometry are both important. Core-shell nanoparticles have a less water-accessible core than PLGA-stabilized double emulsions, for example, and it may be expected that they release drugs more slowly in similar salt/pH conditions. Because water can access ion pairs at the water-vehicle interface much more readily than complexes deep in the vehicle core, release is expected to occur from the outside in. After ion pairs at the surface have been de-complexed and partition into the bulk phase, water will be able to access the complexes deeper in the vehicle. During this 'erosion,' the vehicle itself may lose structural integrity or collapse.⁶¹ For vehicles with low drug loading, the hydrophobic complex's location in the vehicle is another factor to consider. A complex with amphiphilic character that resides primarily on the vehicle surface is easily water-accessible, and rapid burst release may be observed.^{65,97,111}

The fact that de-complexation is a precursor to this type of release explains why slower drug release is seen at higher charge ratios.^{71,78,103} A monovalent drug complexed with a single monovalent counterion should fully dissociate much more quickly than a drug complexed with four, and will not release from the vehicle until it is fully dissociated. In the 1 : 4 charge ratio case, only one of the counterions can truly form an ion pair with the drug (see the preceding section on drug : counterion charge ratio). The remaining three counterions can remain associated with the complex, though, adsorbing onto the first counterion *via* tail-tail hydrophobic interactions. The resulting large hydrophobic surface area serves as a mass transfer barrier that slows water diffusion to the site of ion pairing. For this reason, it is more difficult for water to access and dissociate the 1 : 4 complex than the 1 : 1 complex, so drug release is slower. The probability of a drug re-complexing with a hydrophobic counterion after salt-driven decomplexation also increases with the number of hydrophobic counterions near a drug molecule.

After dissociation, the therapeutic and counterion are regenerated. Without its hydrophobic counterion, the therapeutic is likely too hydrophilic to remain associated with the vehicle (even if the solution pH has turned off the drug's charge) and will partition into the bulk. Depending on its chemistry and the bulk pH, the counterion may either diffuse into the bulk or remain with the vehicle. For example, we found that at a 1 : 4 polymyxin B : oleate charge ratio, drug release plateaued around 35%. This suggests that after soluble polymyxin b was released, the poorly-water-soluble oleate fatty acids remain with the nanoparticle and may form an oleate/oleic acid liquid crystal phase in or around the NP core. This type of plateauing release profile was not observed for polymyxin paired at a 1 : 4 polymyxin : SDS charge ratio, because SDS is more water-soluble and prefers to partition into the bulk.⁷⁸

Complexation formation, dissociation, and release have all been found to be a function of bulk ionic strength.^{18,38,44,45,72,120} As expected, at higher ionic strength, it is more difficult to form complexes due to charge screening, and, if formed, complexes dissociate and drugs are released faster at higher salt concentrations. PBS, sodium chloride, and serum are common release media. Researchers have found both complexation^{18,57,120,121} and release^{30,38,48,70–72,105,112,121} to be pH-dependent. These assays are



usually run at pH values at and below 7.3. In most cases, faster release at lower pH has been observed as expected.

This understanding of the mechanism behind salt- and pH-dependent release is useful. Many nano-scale delivery vehicles are stable in water and can be stored in deionized water without beginning to release their payload. For parenteral or oral formulations, the body's natural ionic strength will trigger release. pH-dependent release could be useful for targeting to endosomes, tumors, or different regions in the intestinal tract. On the other hand, pH sensitivity may rule out some long-term depot delivery strategies; for example, it has been well-documented that PLGA microparticles may acidify as the polymer is degraded over time.^{12,122} An acid microenvironment could trigger ion pair dissociation and lead to faster release.

The previous several paragraphs have discussed drug release following ion pair dissociation. In general, unless a hydrophobic complex is exposed to salts or pH changes, it should behave like a hydrophobic molecule – depending on the vehicle and the chemistry of the species that make up the pair, the complex could still be released intact from the vehicle. Hydrophobic molecules in nano-scale delivery vehicles can diffuse and, depending on their solubility in the release medium, may still partition into the bulk. The complex's size and hydrophobic interactions with the delivery vehicle are barriers to diffusion.^{65,66,116} When buffers containing only salts are used as simple release media, this type of release is unlikely. In more complex, more realistic release media – *i.e.* those containing some kind of hydrophobic sink such as albumins or bile salt micelles – this type of direct release, as well as salt- or pH-driven release, may occur simultaneously. The driving forces for

diffusion of all species, including paired and unpaired drugs and paired, unpaired, and uncharged counterions, should be considered.

It is straightforward to see that both major exit routes from a particle – either following dissociation or as an intact complex – depend on the complex itself and the counterion used. Alkyl tail length or hydrophobic group size, for example, affect both. In the case of post-dissociation release, larger hydrophobic surface areas decrease water permeability and slow decomplexation, as discussed in the paragraph about release as a function of charge ratio. And in the case of release as an intact complex, longer alkyl tails both decrease the complex's solubility in the bulk and increase steric and hydrophobic interactions that tend to keep the complex in its vehicle. As counterion hydrophobicity increases, therefore, release tends to decrease (Fig. 6).^{29,38,65,78,88}

5. Bridging polyelectrolyte coacervation, polymer–surfactant complexation, and hydrophobic ion pairing

The HIP literature has generally not overlapped with the literature from the fields of polyelectrolyte–polyelectrolyte coacervation or polyelectrolyte–surfactant complexation. The fields share a number of similarities that we will highlight here. Polyelectrolyte complex coacervation used here refers to the phase separation induced when oppositely-charged polyelectrolytes or ionomers ion pair with one another, and is not to be confused with the acid-induced lipid precipitation technique mentioned earlier (which is also called ‘coacervation’). Polyelectrolyte–surfactant complexation has been studied extensively and is useful in a number of industrial applications, including personal care products and detergents.¹²³

5.1 Polyelectrolyte coacervation

Ion pairing between polyelectrolyte species results in the formation of a highly electrostatically crosslinked complex that phase separates from its surrounding media; the new phase may be either a solid (‘precipitate’) or liquid (‘coacervate’), but the term ‘complex coacervation’ is applied in both cases.^{124–126} Stoichiometric ratios (*i.e.* 1 : 1 cation : anion) are common in this literature, since these systems tend to form more distinct coacervate phases from charge neutral conditions – at uneven ratios, electrostatically-stabilized colloidal particles may form.¹²⁵ Like hydrophobic ion pairs, coacervate phases are sensitive to salt and may be dissociated at sufficient ionic strength or as a function of pH, depending on the chemistry.

The entropic and enthalpic effects of coacervate formation and phase separation have been studied and reported elsewhere.^{125,127–132} Interestingly, polymers in a complex coacervate may remain mobile, and rearrangement is possible. Many studies focus on the coacervate's phase behaviour¹³³ or rheological¹³⁴ or thermal¹³⁵ properties. The final phase's log *P* (and hydrophobicity in general) is not a major concern in complex

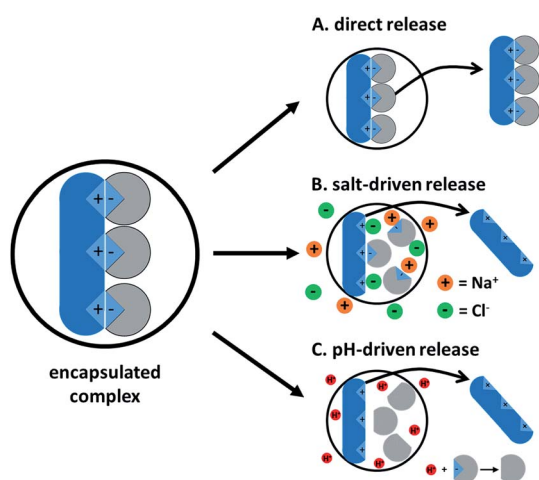


Fig. 6 A summary of how complexed drugs may be released from a delivery vehicle. (A) The intact complex may release directly from the particle into the bulk. This type of release is a function of the complex's solubility in the bulk, so hydrophobic sinks such as bile salt micelles or albumins in the bulk phase will provide more of a driving force than simply a buffer. (B) Salts lead to counterion competition and decomplexation, which is followed by release as the water-soluble drug is released into the bulk. (C) When counterions such as fatty acids are used, lowering the pH below their pK_a will lead to protonation. The protonated counterions will no longer complex the drug, leading to release as in (B).



Polymer-surfactant complexation and phase behavior have been studied for decades.^{142,143} The field has carefully examined precipitate formation as a function of many parameters familiar

S(M/N)	Self-(micro/nano)emulsifying drug delivery system
EDDS	
XRD	X-ray diffraction

Funding

We acknowledge financial support from the Bill and Melinda Gates Foundation (BMGF OPP1150755), The Princeton SEAS Helen Shipley Hunt Fund, and the National Science Foundation for the research fellowship for K. D. R. (DGE-1656466) and (CBET 1605816).

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors thank Dr Nathalie Pinkerton, Dr Robert Pagels, Mr Chester Markwalter, and Mr Douglas Scott for intellectual discussion and for their help reviewing the document.

References

- J. D. Meyer and M. C. Manning, Hydrophobic Ion Pairing: Altering the Solubility Properties of Biomolecules, *Pharm. Res.*, 1998, **15**(2), 188–193.
- T. Wang and X. Wang, Solubilization of an indicator dye for optical fiber chemical sensors in supercritical CO₂ by ion pairing, *Sens. Actuators, B*, 2003, **89**(1), 144–149.
- S. Wu, A. Buthe and P. Wang, Organic-soluble enzyme nano-complexes formed by ion-pairing with surfactants, *Methods Mol. Biol.*, 2011, **743**, 51–63.
- R. Pangen, J. U. Choi, V. K. Panthi, Y. Byun and J. W. Park, Enhanced oral absorption of pemetrexed by ion-pairing complex formation with deoxycholic acid derivative and multiple nanoemulsion formulations: preparation, characterization, and in vivo oral bioavailability and anticancer effect, *Int. J. Nanomed.*, 2018, **13**, 3329–3351.
- S. K. You, H. H. Kwon, J. M. Lee, S. C. Shin and C. W. Cho, Studies on the formation of hydrophobic ion-pairing complex of alendronate, *Arch. Pharmacol. Res.*, 2009, **32**(7), 1055–1060.
- T. N. Q. Phan, I. Shahzadi and A. Bernkop-Schnürch, Hydrophobic ion-pairs and lipid-based nanocarrier systems: the perfect match for delivery of BCS class 3 drugs, *J. Controlled Release*, 2019.
- S. A. Megwa, S. E. Cross, M. W. Whitehouse, H. A. Benson and M. S. Roberts, Effect of ion pairing with alkylamines on the in-vitro dermal penetration and local tissue disposition of salicylates, *J. Pharm. Pharmacol.*, 2000, **52**(8), 929–940.
- A. S. Torky, M. S. Freag, M. M. A. Nasra and O. Y. Abdallah, Novel skin penetrating berberine oleate complex capitalizing on hydrophobic ion pairing approach, *Int. J. Pharm.*, 2018, **549**(1–2), 76–86.
- S. Bonengel, M. Jelkmann, M. Abdulkarim, M. Gumbleton, V. Reinstadler, H. Oberacher, F. Prufert and A. Bernkop-Schnürch, Impact of different hydrophobic ion pairs of octreotide on its oral bioavailability in pigs, *J. Controlled Release*, 2018, **273**, 21–29.
- M. Goswami, S. K. Kumar, A. Bhattacharya and J. F. Douglas, Computer Simulations of Ionomer Self-Assembly and Dynamics, *Macromolecules*, 2007, **40**(12), 4113–4118.
- J. Iqbal, C. Vigl, G. Moser, M. Gasteiger, G. Perera and A. Bernkop-Schnürch, Development and in vivo evaluation of a new oral nanoparticulate dosage form for leuprolide based on polyacrylic acid, *Drug Delivery*, 2011, **18**(6), 432–440.
- R. F. Pagels and R. K. Prud'homme, Polymeric nanoparticles and microparticles for the delivery of peptides, biologics, and soluble therapeutics, *J. Controlled Release*, 2015, **219**, 519–535.
- R. Singh and J. W. Lillard Jr, Nanoparticle-based targeted drug delivery, *Exp. Mol. Pathol.*, 2009, **86**(3), 215–223.
- C. E. Markwalter, R. F. Pagels, B. K. Wilson, K. D. Ristorph and R. K. Prud'homme, Flash NanoPrecipitation for the Encapsulation of Hydrophobic and Hydrophilic Compounds in Polymeric Nanoparticles, *JoVE*, 2019, (143), e58757.
- K. T. Savjani, A. K. Gajjar and J. K. Savjani, Drug solubility: importance and enhancement techniques, *ISRN Pharm.*, 2012, **2012**, 195727.
- S. Kumar, D. Bhargava, A. Thakkar and S. Arora, Drug carrier systems for solubility enhancement of BCS class II drugs: a critical review, *Crit. Rev. Ther. Drug Carrier Syst.*, 2013, **30**(3), 217–256.
- C. Wischke and S. P. Schwendeman, Principles of encapsulating hydrophobic drugs in PLA/PLGA microparticles, *Int. J. Pharm.*, 2008, **364**(2), 298–327.
- B. Devrim and A. S. Bozkir, in *Design and Evaluation of Hydrophobic Ion-Pairing Complexation of Lysozyme with Sodium Dodecyl Sulfate for Improved Encapsulation of Hydrophilic Peptides/Proteins by Lipid-Polymer Hybrid Nanoparticles*, 2015.
- S. M. Ansell, S. A. Johnstone, P. G. Tardi, L. Lo, S. Xie, Y. Shu, T. O. Harasym, N. L. Harasym, L. Williams, D. Bermudes, B. D. Liboiron, W. Saad, R. K. Prud'homme and L. D. Mayer, Modulating the Therapeutic Activity of Nanoparticle Delivered Paclitaxel by Manipulating the Hydrophobicity of Prodrug Conjugates, *J. Med. Chem.*, 2008, **51**(11), 3288–3296.
- J. S. Sohn, J. I. Jin, M. Hess and B. W. Jo, Polymer prodrug approaches applied to paclitaxel, *Polym. Chem.*, 2010, **1**(6), 778–792.
- V. J. Stella, Prodrugs: Some thoughts and current issues, *J. Pharm. Sci.*, 2010, **99**(12), 4755–4765.
- E. E. Dormidontova, Role of Competitive PEO-Water and Water-Water Hydrogen Bonding in Aqueous Solution PEO Behavior, *Macromolecules*, 2002, **35**(3), 987–1001.
- Y. Zhang, S. Furyk, D. E. Bergbreiter and P. S. Cremer, Specific Ion Effects on the Water Solubility of



- Macromolecules: PNIPAM and the Hofmeister Series, *J. Am. Chem. Soc.*, 2005, **127**(41), 14505–14510.
- 24 R. J. Goddard, B. P. Grady and S. L. Cooper, The Room Temperature Annealing Peak in Ionomers: Ionic Crystallites or Water Absorption?, *Macromolecules*, 1994, **27**(7), 1710–1719.
 - 25 B. A. Brozoski, P. C. Painter and M. M. Coleman, Concerning the origin of broad bands observed in the FT-IR spectra of ionomers. Cluster formation or water adsorption?, *Macromolecules*, 1984, **17**(8), 1591–1594.
 - 26 J.-S. Kim and A. Eisenberg, Effect of sample preparation conditions and degree of neutralization on the dynamic mechanical properties of poly(styrene-*co*-sodium methacrylate) ionomers, *J. Polym. Sci., Part B: Polym. Phys.*, 1995, **33**(2), 197–209.
 - 27 S. Yang, K. Sun and W. M. Risen Jr., Preparation and thermal characterization of the glass transition temperatures of sulfonated polystyrene-metal ionomers, *J. Polym. Sci., Part B: Polym. Phys.*, 1990, **28**(10), 1685–1697.
 - 28 M. Morgen, A. Saxena, X. Q. Chen, W. Miller, R. Nkansah, A. Goodwin, J. Cape, R. Haskell, C. Su, O. Gudmundsson, M. Hageman, A. Kumar, G. S. Chowan, A. Rao and V. K. Holenarsipur, Lipophilic salts of poorly soluble compounds to enable high-dose lipidic SEDDS formulations in drug discovery, *Eur. J. Pharm. Biopharm.*, 2017, **117**, 212–223.
 - 29 B. K. Poudel, B. Gupta, T. Ramasamy, R. K. Thapa, Y. S. Youn, H. G. Choi, C. S. Yong and J. O. Kim, Development of polymeric irinotecan nanoparticles using a novel lactone preservation strategy, *Int. J. Pharm.*, 2016, **512**(1), 75–86.
 - 30 Z. Zhou, M. Jafari, V. Sriram, J. Kim and J. Y. Lee, Delayed Sequential Co-Delivery of Gefitinib and Doxorubicin for Targeted Combination, *Chemotherapy*, 2017, **14**(12), 4551–4559.
 - 31 P. R. Cullis and M. J. Hope, Lipid Nanoparticle Systems for Enabling Gene Therapies, *Mol. Ther.*, 2017, **25**(7), 1467–1475.
 - 32 L. Xu and T. Anchordoquy, Drug delivery trends in clinical trials and translational medicine: Challenges and opportunities in the delivery of nucleic acid-based therapeutics, *J. Pharm. Sci.*, 2011, **100**(1), 38–52.
 - 33 M. A. Mintzer and E. E. Simanek, Nonviral Vectors for Gene Delivery, *Chem. Rev.*, 2009, **109**(2), 259–302.
 - 34 K. A. Whitehead, R. Langer and D. G. Anderson, Knocking down barriers: advances in siRNA delivery, *Nat. Rev. Drug Discovery*, 2009, **8**(2), 129–138.
 - 35 W. Li and F. C. Szoka, Lipid-based Nanoparticles for Nucleic Acid Delivery, *Pharm. Res.*, 2007, **24**(3), 438–449.
 - 36 S. A. Wissing, O. Kayser and R. H. Muller, Solid lipid nanoparticles for parenteral drug delivery, *Adv. Drug Delivery Rev.*, 2004, **56**(9), 1257–1272.
 - 37 W. Mehnert and K. Mader, Solid lipid nanoparticles: production, characterization and applications, *Adv. Drug Delivery Rev.*, 2001, **47**(2–3), 165–196.
 - 38 Y. H. Song, E. Shin, H. Wang, J. Nolan, S. Low, D. Parsons, S. Zale, S. Ashton, M. Ashford, M. Ali, D. Thrasher, N. Boylan and G. Troiano, A novel in situ hydrophobic ion pairing (HIP) formulation strategy for clinical product selection of a nanoparticle drug delivery system, *J. Controlled Release*, 2016, **229**, 106–119.
 - 39 M. J. Heffernan, S. P. Kasturi, S. C. Yang, B. Pulendran and N. Murthy, The stimulation of CD8⁺ T cells by dendritic cells pulsed with polyketal microparticles containing ion-paired protein antigen and poly(inosinic acid)-poly(cytidylic acid), *Biomaterials*, 2009, **30**(5), 910–918.
 - 40 T. Satoh, Y. Higuchi, S. Kawakami, M. Hashida, H. Kagechika, K. Shudo and M. Yokoyama, Encapsulation of the synthetic retinoids Am80 and LE540 into polymeric micelles and the retinoids' release control, *J. Controlled Release*, 2009, **136**(3), 187–195.
 - 41 I. Shahzadi, M. H. Asim, A. Dizdarević, J. D. Wolf, M. Kurpiers, B. Matuszczak and A. Bernkop-Schnürch, Arginine-based cationic surfactants: Biodegradable auxiliary agents for the formation of hydrophobic ion pairs with hydrophilic macromolecular drugs, *J. Colloid Interface Sci.*, 2019, **552**, 287–294.
 - 42 T. Karamanidou, K. Karidi, V. Bourganis, K. Kontonikola, O. Kammona and C. Kiparissides, Effective incorporation of insulin in mucus permeating self-nanoemulsifying drug delivery systems, *Eur. J. Pharm. Biopharm.*, 2015, **97**(Pt A), 223–229.
 - 43 H. D. Lu, K. D. Ristroph, E. L. K. Dobrijevic, J. Feng, S. A. McManus, Y. Zhang, W. D. Mulhearn, H. Ramachandruni, A. Patel and R. K. Prud'homme, Encapsulation of OZ439 into Nanoparticles for Supersaturated Drug Release in Oral Malaria Therapy, *ACS Infect. Dis.*, 2018.
 - 44 L. Feng, A. De Dille, V. J. Jameson, L. Smith, W. S. Dernell and M. C. Manning, Improved potency of cisplatin by hydrophobic ion pairing, *Cancer Chemother. Pharmacol.*, 2004, **54**(5), 441–448.
 - 45 J. Chamieh, A. Domènech Tarrat, C. Doudou, V. Jannin, F. Demarne and H. Cottet, Peptide release from SEDDS containing hydrophobic ion pair therapeutic peptides measured by Taylor dispersion analysis, *Int. J. Pharm.*, 2019, **559**, 228–234.
 - 46 G. A. Castro, A. L. Coelho, C. A. Oliveira, G. A. Mahecha, R. L. Orefice and L. A. Ferreira, Formation of ion pairing as an alternative to improve encapsulation and stability and to reduce skin irritation of retinoic acid loaded in solid lipid nanoparticles, *Int. J. Pharm.*, 2009, **381**(1), 77–83.
 - 47 N. M. Pinkerton, A. Grandeury, A. Fisch, J. Brozio, B. U. Riebeschl and R. K. Prud'homme, Formation of stable nanocarriers by in situ ion pairing during block-copolymer-directed rapid precipitation, *Mol. Pharm.*, 2013, **10**(1), 319–328.
 - 48 K. Patel, V. Sarma and P. Vavia, Design and evaluation of lumefantrine – oleic acid self nanoemulsifying ionic complex for enhanced dissolution, *Daru, J. Fac. Pharm., Tehran Univ. Med. Sci.*, 2013, **21**(1), 27.
 - 49 R. Bussano, D. Chirio, L. Costa, F. Turci and M. Trotta, Preparation and Characterization of Insulin-Loaded Lipid-



- Based Microspheres Generated by Electrospray, *J. Dispersion Sci. Technol.*, 2011, **32**(10), 1524–1530.
- 50 W. G. Dai and L. C. Dong, Characterization of physiochemical and biological properties of an insulin/lauryl sulfate complex formed by hydrophobic ion pairing, *Int. J. Pharm.*, 2007, **336**(1), 58–66.
 - 51 S. Sun, F. Cui, Y. Kawashima, N. Liang, L. Zhang, K. Shi and Y. Yu, A novel insulin-sodium oleate complex for oral administration: preparation, characterization and in vivo evaluation, *J. Drug Delivery Sci. Technol.*, 2008, **18**(4), 239–243.
 - 52 F. Cui, K. Shi, L. Zhang, A. Tao and Y. Kawashima, Biodegradable nanoparticles loaded with insulin-phospholipid complex for oral delivery: preparation, in vitro characterization and in vivo evaluation, *J. Controlled Release*, 2006, **114**(2), 242–250.
 - 53 A. Elsayed, M. Al-Remawi, N. Qinna, A. Farouk, K. A. Al-Sou'od and A. A. Badwan, Chitosan-sodium lauryl sulfate nanoparticles as a carrier system for the in vivo delivery of oral insulin, *AAPS PharmSciTech*, 2011, **12**(3), 958–964.
 - 54 K. Talley and E. Alexov, On the pH-optimum of activity and stability of proteins, *Proteins*, 2010, **78**(12), 2699–2706.
 - 55 D. Otzen, Protein-surfactant interactions: a tale of many states, *Biochim. Biophys. Acta*, 2011, **1814**(5), 562–591.
 - 56 K. Fu, R. Harrell, K. Zinski, C. Um, A. Jaklenec, J. Frazier, N. Lotan, P. Burke, A. M. Klibanov and R. Langer, A potential approach for decreasing the burst effect of protein from PLGA microspheres, *J. Pharm. Sci.*, 2003, **92**(8), 1582–1591.
 - 57 H. S. Yoo, H. K. Choi and T. G. Park, Protein-fatty acid complex for enhanced loading and stability within biodegradable nanoparticles, *J. Pharm. Sci.*, 2001, **90**(2), 194–201.
 - 58 U. Bilati, E. Allemann and E. Doelker, Nanoprecipitation versus emulsion-based techniques for the encapsulation of proteins into biodegradable nanoparticles and process-related stability issues, *AAPS PharmSciTech*, 2005, **6**(4), E594–E604.
 - 59 R. Gaudana, M. Gokulgandhi, V. Khurana, D. Kwatra and A. K. Mitra, Design and evaluation of a novel nanoparticulate-based formulation encapsulating a HIP complex of lysozyme, *Pharm. Dev. Technol.*, 2013, **18**(3), 752–759.
 - 60 H. Zhou, C. Lengsfeld, D. J. Claffey, J. A. Ruth, B. Hybertson, T. W. Randolph, K. Y. Ng and M. C. Manning, Hydrophobic ion pairing of isoniazid using a prodrug approach, *J. Pharm. Sci.*, 2002, **91**(6), 1502–1511.
 - 61 H. L. Wong, R. Bendayan, A. M. Rauth and X. Y. Wu, Development of solid lipid nanoparticles containing ionically complexed chemotherapeutic drugs and chemosensitizers, *J. Pharm. Sci.*, 2004, **93**(8), 1993–2008.
 - 62 Database., N. C. f. B. I. P. Sodium oleate, CID=23665730. <https://pubchem.ncbi.nlm.nih.gov/compound/23665730>.
 - 63 Database., N. C. f. B. I. P. Oleic acid, CID=445639. <https://pubchem.ncbi.nlm.nih.gov/compound/445639>.
 - 64 R. S. Kalhapure, C. Mocktar, D. R. Sikwal, S. J. Sonawane, M. K. Kathiravan, A. Skelton and T. Govender, Ion pairing with linoleic acid simultaneously enhances encapsulation efficiency and antibacterial activity of vancomycin in solid lipid nanoparticles, *Colloids Surf., B*, 2014, **117**, 303–311.
 - 65 G. Carneiro, E. L. Silva, L. A. Pacheco, E. M. de Souza-Fagundes, N. C. Correa, A. M. de Goes, M. C. de Oliveira and L. A. Ferreira, Formation of ion pairing as an alternative to improve encapsulation and anticancer activity of all-trans retinoic acid loaded in solid lipid nanoparticles, *Int. J. Nanomed.*, 2012, **7**, 6011–6020.
 - 66 W. Yin, Z. Dong, X. Chen, N. Finn and M. Z. Yates, Hydrophobic ion pairing to enhance encapsulation of water-soluble additives into CO₂-swollen polymer microparticles, *J. Supercrit. Fluids*, 2007, **41**(2), 293–298.
 - 67 D. E. Kuehner, J. Engmann, F. Fergg, M. Wernick, H. W. Blanch and J. M. Prausnitz, Lysozyme Net Charge and Ion Binding in Concentrated Aqueous Electrolyte Solutions, *J. Phys. Chem. B*, 1999, **103**(8), 1368–1374.
 - 68 V. Spassov and L. Yan, *A pH-dependent computational approach to the effect of mutations on protein stability*, 2016, vol. 37.
 - 69 G. Yu, J. Liu and J. Zhou, Mesoscopic coarse-grained simulations of hydrophobic charge induction chromatography (HCIC) for protein purification, *AIChE J.*, 2015, **61**(6), 2035–2047.
 - 70 S. V. Mussi, R. C. Silva, M. C. Oliveira, C. M. Lucci, R. B. Azevedo and L. A. Ferreira, New approach to improve encapsulation and antitumor activity of doxorubicin loaded in solid lipid nanoparticles, *Eur. J. Pharm. Sci.*, 2013, **48**(1–2), 282–290.
 - 71 Z. Zhou, C. Kennell, M. Jafari, J. Y. Lee, S. J. Ruiz-Torres, S. E. Waltz and J. H. Lee, Sequential delivery of erlotinib and doxorubicin for enhanced triple negative Breast cancer treatment using polymeric nanoparticle, *Int. J. Pharm.*, 2017, **530**(1–2), 300–307.
 - 72 A. Siddiqui, V. Gupta, Y. Y. Liu and S. Nazzal, Doxorubicin and MBO-asGCS oligonucleotide loaded lipid nanoparticles overcome multidrug resistance in adriamycin resistant ovarian cancer cells (NCI/ADR-RES), *Int. J. Pharm.*, 2012, **431**(1–2), 222–229.
 - 73 J. K. Guillery, *Handbook of Pharmaceutical Salts: Properties, Selection, and Use* Edited by P. Heinrich Stahl and Camile G. Wermuth. VCH, Verlag Helvetica Chimica Acta, Zürich, Switzerland, and Wiley-VCH, Weinheim, Germany. 2002. vix + 374 pp. 17.5 × 24.5 cm. ISBN 3-906390-26-8. \$130.00, *J. Med. Chem.*, 2003, **46**(7), 1277.
 - 74 W. Q. Tong and G. Whitesell, In situ salt screening—a useful technique for discovery support and preformulation studies, *Pharm. Dev. Technol.*, 1998, **3**(2), 215–223.
 - 75 I. Ghosh and W. M. Nau, The strategic use of supramolecular pKa shifts to enhance the bioavailability of drugs, *Adv. Drug Delivery Rev.*, 2012, **64**(9), 764–783.
 - 76 N. i. Saleh, A. L. Koner and W. M. Nau, Activation and Stabilization of Drugs by Supramolecular pKa Shifts: Drug-Delivery Applications Tailored for Cucurbiturils, *Angew. Chem., Int. Ed.*, 2008, **47**(29), 5398–5401.
 - 77 O. Zupancic, G. Leonaviciute, H. T. Lam, A. Partenhauser, S. Podricnik and A. Bernkop-Schnurch, Development and



- in vitro evaluation of an oral SEDDS for desmopressin, *Drug Delivery*, 2016, **23**(6), 2074–2083.
- 78 H. D. Lu, P. Rummaneeethorn, K. D. Ristroph and R. K. Prud'homme, Hydrophobic Ion Pairing of Peptide Antibiotics for Processing into Controlled Release Nanocarrier Formulations, *Mol. Pharm.*, 2018, **15**(1), 216–225.
 - 79 S. Zafar, L. M. Negi, A. K. Verma, V. Kumar, A. Tyagi, P. Singh, Z. Iqbal and S. Talegaonkar, Sterically stabilized polymeric nanoparticles with a combinatorial approach for multi drug resistant cancer: in vitro and in vivo investigations, *Int. J. Pharm.*, 2014, **477**(1–2), 454–468.
 - 80 R. Rastogi, S. Anand and V. Koul, Evaluation of pharmacological efficacy of 'insulin-surfoplex' encapsulated polymer vesicles, *Int. J. Pharm.*, 2009, **373**(1–2), 107–115.
 - 81 J. Fu, F. Sun, W. Liu, Y. Liu, M. Gedam, Q. Hu, C. Fridley, H. A. Quigley, J. Hanes and I. Pitha, Subconjunctival Delivery of Dorzolamide-Loaded Poly(ether-anhydride) Microparticles Produces Sustained Lowering of Intraocular Pressure in Rabbits, *Mol. Pharm.*, 2016, **13**(9), 2987–2995.
 - 82 E. Imbuluzqueta, E. Elizondo, C. Gamazo, E. Moreno-Calvo, J. Veciana, N. Ventosa and M. J. Blanco-Prieto, Novel bioactive hydrophobic gentamicin carriers for the treatment of intracellular bacterial infections, *Acta Biomater.*, 2011, **7**(4), 1599–1608.
 - 83 M. Gallarate, M. Trotta, L. Battaglia and D. Chirio, Cisplatin-loaded SLN produced by coacervation technique, *J. Drug Delivery Sci. Technol.*, 2010, **20**(5), 343–347.
 - 84 M. Gallarate, L. Battaglia, E. Peira and M. Trotta, Peptide-Loaded Solid Lipid Nanoparticles Prepared through Coacervation Technique, *Int. J. Chem. Eng.*, 2011, **2011**, 6.
 - 85 H. Sang Yoo and T. Gwan Park, Biodegradable nanoparticles containing protein-fatty acid complexes for oral delivery of salmon calcitonin, *J. Pharm. Sci.*, 2004, **93**(2), 488–495.
 - 86 J. Griesser, G. Hetenyi, M. Moser, F. Demarne, V. Jannin and A. Bernkop-Schnurch, Hydrophobic ion pairing: Key to highly payloaded self-emulsifying peptide drug delivery systems, *Int. J. Pharm.*, 2017, **520**(1–2), 267–274.
 - 87 H. Yuan, S. P. Jiang, Y. Z. Du, J. Miao, X. G. Zhang and F. Q. Hu, Strategic approaches for improving entrapment of hydrophilic peptide drugs by lipid nanoparticles, *Colloids Surf., B*, 2009, **70**(2), 248–253.
 - 88 V. Jain, D. Singodia, G. K. Gupta, D. Garg, G. B. S. Keshava, R. Shukla, P. K. Shukla and P. R. Mishra, Ciprofloxacin surfplexes in sub-micron emulsions: A novel approach to improve payload efficiency and antimicrobial efficacy, *Int. J. Pharm.*, 2011, **409**(1), 237–244.
 - 89 S. Ashton, Y. H. Song, J. Nolan, E. Cadogan, J. Murray, R. Odedra, J. Foster, P. A. Hall, S. Low, P. Taylor, R. Ellston, U. M. Polanska, J. Wilson, C. Howes, A. Smith, R. J. A. Goodwin, J. G. Swales, N. Strittmatter, Z. Takáts, A. Nilsson, P. Andren, D. Trueman, M. Walker, C. L. Reimer, G. Troiano, D. Parsons, D. De Witt, M. Ashford, J. Hrkach, S. Zale, P. J. Jewsbury and S. T. Barry, Aurora kinase inhibitor nanoparticles target tumors with favorable therapeutic index in vivo, *Sci. Transl. Med.*, 2016, **8**(325), 325ra17.
 - 90 A. Patel, R. Gaudana and A. K. Mitra, A novel approach for antibody nanocarriers development through hydrophobic ion-pairing complexation, *J. Microencapsulation*, 2014, **31**(6), 542–550.
 - 91 R. Gaudana, V. Khurana, A. Parenky and A. K. Mitra, Encapsulation of Protein-Polysaccharide HIP Complex in Polymeric Nanoparticles, *J. Drug Delivery*, 2011, **2011**.
 - 92 R. D. Vaishya, A. Mandal, M. Gokulgandhi, S. Patel and A. K. Mitra, Reversible hydrophobic ion-pairing complex strategy to minimize acylation of octreotide during long-term delivery from PLGA microparticles, *Int. J. Pharm.*, 2015, **489**(1–2), 237–245.
 - 93 S. Sun, N. Liang, Y. Kawashima, D. Xia and F. Cui, Hydrophobic ion pairing of an insulin-sodium deoxycholate complex for oral delivery of insulin, *Int. J. Nanomed.*, 2011, **6**, 3049–3056.
 - 94 F. Hintzen, G. Perera, S. Hauptstein, C. Muller, F. Laffleur and A. Bernkop-Schnurch, In vivo evaluation of an oral self-microemulsifying drug delivery system (SMEDDS) for leuporelin, *Int. J. Pharm.*, 2014, **472**(1–2), 20–26.
 - 95 P. Ma, X. Dong, C. L. Swadley, A. Gupte, M. Leggas, H. C. Ledebur and R. J. Mumper, Development of idarubicin and doxorubicin solid lipid nanoparticles to overcome Pgp-mediated multiple drug resistance in leukemia, *J. Biomed. Nanotechnol.*, 2009, **5**(2), 151–161.
 - 96 R. Mahjub, F. A. Dorkoosh, M. Rafiee-Tehrani and A. Bernkop-Schnurch, Oral self-nanoemulsifying peptide drug delivery systems: impact of lipase on drug release, *J. Microencapsulation*, 2015, **32**(4), 401–407.
 - 97 C. Lechner, C. Menzel, F. Laffleur and A. Bernkop-Schnurch, Development and in vitro characterization of a papain loaded mucolytic self-emulsifying drug delivery system (SEDDS), *Int. J. Pharm.*, 2017, **530**(1–2), 346–353.
 - 98 M. Ijaz, S. Bonengel, O. Zupancic, M. Yaqoob, M. Hartl, S. Hussain, C. W. Huck and A. Bernkop-Schnurch, Development of oral self nano-emulsifying delivery system(s) of lanreotide with improved stability against presystemic thiol-disulfide exchange reactions, *Expert Opin. Drug Delivery*, 2016, **13**(7), 923–929.
 - 99 A. Adjei, S. Rao, J. Garren, G. Menon and M. Vadnere, Effect of ion-pairing on 1-octanol-water partitioning of peptide drugs. I: the nonapeptide leuprolide acetate, *Int. J. Pharm.*, 1993, **90**(2), 141–149.
 - 100 M. E. Powers, J. Matsuura, J. Brassell, M. C. Manning and E. Shefter, Enhanced solubility of proteins and peptides in nonpolar solvents through hydrophobic ion pairing, *Biopolymers*, 1993, **33**(6), 927–932.
 - 101 S. H. Choi and T. G. Park, Hydrophobic ion pair formation between leuprolide and sodium oleate for sustained release from biodegradable polymeric microspheres, *Int. J. Pharm.*, 2000, **203**(1–2), 193–202.
 - 102 S. Sun, N. Liang, H. Piao, H. Yamamoto, Y. Kawashima and F. Cui, Insulin-S.O (sodium oleate) complex-loaded PLGA



- nanoparticles: formulation, characterization and in vivo evaluation, *J. Microencapsulation*, 2010, **27**(6), 471–478.
- 103 H. M. Abdelaziz, A. O. Elzoghby, M. W. Helmy, M. W. Samaha, J. Y. Fang and M. S. Freag, Liquid crystalline assembly for potential combinatorial chemotherapeutic drug delivery to lung cancer cells, *Int. J. Nanomed.*, 2019, **14**, 499–517.
 - 104 G. Dalwadi and B. Sunderland, An ion pairing approach to increase the loading of hydrophilic and lipophilic drugs into PEGylated PLGA nanoparticles, *Eur. J. Pharm. Biopharm.*, 2009, **71**(2), 231–242.
 - 105 M. S. Oliveira, S. V. Mussi, D. A. Gomes, M. I. Yoshida, F. Frezard, V. M. Carregal and L. A. M. Ferreira, alpha-Tocopherol succinate improves encapsulation and anticancer activity of doxorubicin loaded in solid lipid nanoparticles, *Colloids Surf., B*, 2016, **140**, 246–253.
 - 106 X. Zhang, X. Sun, J. Li, X. Zhang, T. Gong and Z. Zhang, Lipid nanoemulsions loaded with doxorubicin-oleic acid ionic complex: characterization, in vitro and in vivo studies, *Pharmazie*, 2011, **66**(7), 496–505.
 - 107 G. A. Castro, R. L. Orefice, J. M. Vilela, M. S. Andrade and L. A. Ferreira, Development of a new solid lipid nanoparticle formulation containing retinoic acid for topical treatment of acne, *J. Microencapsulation*, 2007, **24**(5), 395–407.
 - 108 E. L. Silva, G. Carneiro, P. A. Caetano, G. Goulart, D. Ferreira Costa, E. M. de Souza-Fagundes, D. A. Gomes and L. A. Ferreira, Nanostructured lipid carriers loaded with tributyrin as an alternative to improve anticancer activity of all-trans retinoic acid, *Expert Rev. Anticancer Ther.*, 2015, **15**(2), 247–256.
 - 109 L. Yang, F. Cui, K. Shi, D. Cun and R. Wang, Design of high payload PLGA nanoparticles containing melittin/sodium dodecyl sulfate complex by the hydrophobic ion-pairing technique, *Drug Dev. Ind. Pharm.*, 2009, **35**(8), 959–968.
 - 110 C. Dumont, S. Bourgeois, H. Fessi, P. Y. Dugas and V. Jannin, In-vitro evaluation of solid lipid nanoparticles: Ability to encapsulate, release and ensure effective protection of peptides in the gastrointestinal tract, *Int. J. Pharm.*, 2019, **565**, 409–418.
 - 111 K. Shi, F. Cui, H. Yamamoto and Y. Kawashima, Investigation of drug loading and in vitro release mechanisms of insulin-lauryl sulfate complex loaded PLGA nanoparticles, *Pharmazie*, 2008, **63**(12), 866–871.
 - 112 H. Xu, L. Zhang, L. Li, Y. Liu, Y. Chao, X. Liu, Z. Jin, Y. Chen, X. Tang, H. He, Q. Kan and C. Cai, Membrane-Loaded Doxorubicin Liposomes Based on Ion-Pairing Technology with High Drug Loading and pH-Responsive Property, *AAPS PharmSciTech*, 2017, **18**(6), 2120–2130.
 - 113 H. D. Lu, K. D. Ristoph, E. L. K. Dobrijevic, J. Feng, S. A. McManus, Y. Zhang, W. D. Mulhearn, H. Ramachandruni, A. Patel and R. K. Prud'homme, Encapsulation of OZ439 into Nanoparticles for Supersaturated Drug Release in Oral Malaria Therapy, *ACS Infect. Dis.*, 2018, **4**(6), 970–979.
 - 114 G. A. Castro, L. A. M. Ferreira, R. L. Oréface and V. T. L. Bueno, Characterization of a new solid lipid nanoparticle formulation containing retinoic acid for topical treatment of acne, *Powder Diff.*, 2012, **23**(S1), S30–S35.
 - 115 E. L. Silva, F. A. Lima, G. Carneiro, P. Ramos Jonas, D. A. Gomes, E. M. de Souza-Fagundes and L. A. Ferreira, Improved In Vitro Antileukemic Activity of All-Trans Retinoic Acid Loaded in Cholesteryl Butyrate Solid Lipid Nanoparticles, *J. Nanosci. Nanotechnol.*, 2016, **16**(2), 1291–1300.
 - 116 L. Battaglia, M. Gallarate, E. Peira, D. Chirio, E. Muntoni, E. Biasibetti, M. T. Capucchio, A. Valazza, P. P. Panciani, M. Lanotte, D. Schiffer, L. Annovazzi, V. Caldera, M. Mellai and C. Riganti, Solid lipid nanoparticles for potential doxorubicin delivery in glioblastoma treatment: preliminary in vitro studies, *J. Pharm. Sci.*, 2014, **103**(7), 2157–2165.
 - 117 R. Falk, T. W. Randolph, J. D. Meyer, R. M. Kelly and M. Manning, *Controlled release of ionic compounds from poly (L-lactide) microspheres produced by precipitation with a compressed antisolvent*, 1997, vol. 44, pp. 77–85.
 - 118 E. Elizondo, S. Sala, E. Imbuluzqueta, D. Gonzalez, M. J. Blanco-Prieto, C. Gamazo, N. Ventosa and J. Veciana, High loading of gentamicin in bioadhesive PVM/MA nanostructured microparticles using compressed carbon-dioxide, *Pharm. Res.*, 2011, **28**(2), 309–321.
 - 119 E. Imbuluzqueta, S. Lemaire, C. Gamazo, E. Elizondo, N. Ventosa, J. Veciana, F. Van Bambeke and M. J. Blanco-Prieto, Cellular pharmacokinetics and intracellular activity against *Listeria monocytogenes* and *Staphylococcus aureus* of chemically modified and nanoencapsulated gentamicin, *J. Antimicrob. Chemother.*, 2012, **67**(9), 2158–2164.
 - 120 R. Gaudana, A. Parenky, R. Vaishya, S. K. Samanta and A. K. Mitra, Development and characterization of nanoparticulate formulation of a water soluble prodrug of dexamethasone by HIP complexation, *J. Microencapsulation*, 2011, **28**(1), 10–20.
 - 121 S. Zhao, L. V. Minh, N. Li, V. M. Garamus, U. A. Handge, J. Liu, R. Zhang, R. Willumeit-Romer and A. Zou, Doxorubicin hydrochloride-oleic acid conjugate loaded nanostructured lipid carriers for tumor specific drug release, *Colloids Surf., B*, 2016, **145**, 95–103.
 - 122 K. Fu, D. W. Pack, A. M. Klibanov and R. Langer, Visual Evidence of Acidic Environment Within Degrading Poly(lactic-co-glycolic acid) (PLGA) Microspheres, *Pharm. Res.*, 2000, **17**(1), 100–106.
 - 123 E. D. Goddard, Polymer/surfactant interaction—Its relevance to detergent systems, *J. Am. Oil Chem. Soc.*, 1994, **71**(1), 1–16.
 - 124 J. T. G. Overbeek and M. J. Voorn, Phase separation in polyelectrolyte solutions. Theory of complex coacervation, *J. Cell. Comp. Physiol.*, 1957, **49**(S1), 7–26.
 - 125 J. v. d. Gucht, E. Spruijt, M. Lemmers and M. A. Cohen Stuart, Polyelectrolyte complexes: Bulk phases and colloidal systems, *J. Colloid Interface Sci.*, 2011, **361**(2), 407–422.



- 126 N. R. Johnson and Y. Wang, Coacervate delivery systems for proteins and small molecule drugs, *Expert Opin. Drug Delivery*, 2014, **11**(12), 1829–1832.
- 127 J. Lee, Y. O. Popov and G. H. Fredrickson, Complex coacervation: A field theoretic simulation study of polyelectrolyte complexation, *J. Chem. Phys.*, 2008, **128**(22), 224908.
- 128 K. T. Delaney and G. H. Fredrickson, Theory of polyelectrolyte complexation—complex coacervates are self-coacervates, *J. Chem. Phys.*, 2017, **146**(22), 224902.
- 129 P. Pincus, Colloid stabilization with grafted polyelectrolytes, *Macromolecules*, 1991, **24**(10), 2912–2919.
- 130 Y. O. Popov, J. Lee and G. H. Fredrickson, Field-theoretic simulations of polyelectrolyte complexation, *J. Polym. Sci., Part B: Polym. Phys.*, 2007, **45**(24), 3223–3230.
- 131 M. Muthukumar, 50th Anniversary Perspective: A Perspective on Polyelectrolyte Solutions, *Macromolecules*, 2017, **50**(24), 9528–9560.
- 132 P. Guenoun, H. T. Davis, M. Tirrell and J. W. Mays, Aqueous Micellar Solutions of Hydrophobically Modified Polyelectrolytes, *Macromolecules*, 1996, **29**(11), 3965–3969.
- 133 Q. Wang and J. B. Schlenoff, The Polyelectrolyte Complex/Coacervate Continuum, *Macromolecules*, 2014, **47**(9), 3108–3116.
- 134 W. Xiong, C. Ren, W. Jin, J. Tian, Y. Wang, B. R. Shah, J. Li and B. Li, Ovalbumin-chitosan complex coacervation: Phase behavior, thermodynamic and rheological properties, *Food Hydrocolloids*, 2016, **61**, 895–902.
- 135 Y. Zhang, F. Li, L. D. Valenzuela, M. Sammalkorpi and J. L. Lutkenhaus, Effect of Water on the Thermal Transition Observed in Poly(allylamine hydrochloride)–Poly(acrylic acid) Complexes, *Macromolecules*, 2016, **49**(19), 7563–7570.
- 136 H. K. Awada, N. R. Johnson and Y. Wang, Dual Delivery of Vascular Endothelial Growth Factor and Hepatocyte Growth Factor Coacervate Displays Strong Angiogenic Effects, *Macromol. Biosci.*, 2014, **14**(5), 679–686.
- 137 H. Bysell, P. Hansson and M. Malmsten, Effect of Charge Density on the Interaction between Cationic Peptides and Oppositely Charged Microgels, *J. Phys. Chem. B*, 2010, **114**(21), 7207–7215.
- 138 A. Nolles, A. H. Westphal, J. A. de Hoop, R. G. Fokkink, J. M. Kleijn, W. J. H. van Berkel and J. W. Borst, Encapsulation of GFP in Complex Coacervate Core Micelles, *Biomacromolecules*, 2015, **16**(5), 1542–1549.
- 139 C. B. Packhaeuser and T. Kissel, On the design of in situ forming biodegradable parenteral depot systems based on insulin loaded dialkylaminoalkyl-amine-poly(vinyl alcohol)-g-poly(lactide-co-glycolide) nanoparticles, *J. Controlled Release*, 2007, **123**(2), 131–140.
- 140 A. Obermeyer, E. C. Mills, X.-H. Dong, R. J. Flores and B. Olsen, *Complex coacervation of supercharged proteins with polyelectrolytes*, 2016, vol. 12.
- 141 K. A. Black, D. Priftis, S. L. Perry, J. Yip, W. Y. Byun and M. Tirrell, Protein Encapsulation via Polypeptide Complex Coacervation, *ACS Macro Lett.*, 2014, **3**(10), 1088–1091.
- 142 M. N. Jones, The interaction of sodium dodecyl sulfate with polyethylene oxide, *J. Colloid Interface Sci.*, 1967, **23**(1), 36–42.
- 143 E. D. Goddard and R. B. Hannan, Cationic polymer/anionic surfactant interactions, *J. Colloid Interface Sci.*, 1976, **55**(1), 73–79.
- 144 R. Y. Lochhead and L. R. Huisinga, *A brief review of polymer/surfactant interaction*, Feb 2004.
- 145 M. S. Johal and P. A. Chiarelli, Polymer–surfactant complexation in polyelectrolyte multilayer assemblies, *Soft Matter*, 2007, **3**(1), 34–46.
- 146 E. D. Goddard and R. B. Hannan, Polymer/surfactant interactions, *J. Am. Oil Chem. Soc.*, 1977, **54**(12), 561–566.
- 147 M. Goswami, J. M. Borreguero, P. A. Pincus and B. G. Sumpter, Surfactant-Mediated Polyelectrolyte Self-Assembly in a Polyelectrolyte–Surfactant Complex, *Macromolecules*, 2015, **48**(24), 9050–9059.
- 148 Y. Wang, K. Kimura, Q. Huang, P. L. Dubin and W. Jaeger, Effects of Salt on Polyelectrolyte–Micelle Coacervation, *Macromolecules*, 1999, **32**(21), 7128–7134.
- 149 M. Manuszak Guerrini, R. Lochhead and W. Daly, *Interactions of aminoalkylcarbamoyl cellulose derivatives and sodium dodecyl sulfate. 2. Foam stabilization*, 1999, vol. 147, pp. 67–78.
- 150 M. Antonietti, J. Conrad and A. Thuenemann, Polyelectrolyte–Surfactant Complexes: A New Type of Solid, Mesomorphous Material, *Macromolecules*, 1994, **27**(21), 6007–6011.
- 151 J. Fundin and W. Brown, Polymer/Surfactant Interactions. Sodium Poly(styrene sulfonate) and CTAB Complex Formation. Light Scattering Measurements in Dilute Aqueous Solution, *Macromolecules*, 1994, **27**(18), 5024–5031.
- 152 Â. M. L. Denadai, A. M. de Oliveira, I. M. P. Daniel, L. A. Carneiro, K. C. Ribeiro, H. d. O. Beraldo, K. J. R. da Costa, V. C. da Cunha, M. E. Cortés and R. D. Sinisterra, Chlorhexidine/losartan ionic pair binding and its nanoprecipitation: physico-chemical characterisation and antimicrobial activity, *Supramol. Chem.*, 2012, **24**(3), 204–212.
- 153 W. Li, X. Yi, X. Liu, Z. Zhang, Y. Fu and T. Gong, Hyaluronic acid ion-pairing nanoparticles for targeted tumor therapy, *J. Controlled Release*, 2016, **225**, 170–182.
- 154 K. D. Ristroph, J. Feng, S. A. McManus, Y. Zhang, K. Gong, H. Ramachandruni, C. E. White and R. K. Prud'homme, Spray drying OZ439 nanoparticles to form stable, water-dispersible powders for oral malaria therapy, *J. Transl. Med.*, 2019, **17**(1), 97.
- 155 I. Lozoya-Agullo, M. Planelles, M. Merino-Sanjuán, M. Bermejo, B. Sarmento, I. González-Álvarez and M. González-Álvarez, Ion-pair approach coupled with nanoparticle formation to increase bioavailability of a low permeability charged drug, *Int. J. Pharm.*, 2019, **557**, 36–42.
- 156 C. Tang, E. Zhang, Y. Li and L. Yang, An innovative method for preparation of hydrophobic ion-pairing colistin entrapped poly(lactic acid) nanoparticles: Loading and



- release mechanism study, *Eur. J. Pharm. Sci.*, 2017, **102**, 63–70.
- 157 J. Liu, T. Gong, C. Wang, Z. Zhong and Z. Zhang, Solid lipid nanoparticles loaded with insulin by sodium cholate-phosphatidylcholine-based mixed micelles: preparation and characterization, *Int. J. Pharm.*, 2007, **340**(1–2), 153–162.
 - 158 G. P. Zara, R. Cavalli, A. Fundaro, A. Bargoni, O. Caputo and M. R. Gasco, Pharmacokinetics of doxorubicin incorporated in solid lipid nanospheres (SLN), *Pharmacol. Res.*, 1999, **40**(3), 281–286.
 - 159 S. Morel, E. Ugazio, R. Cavalli and M. R. Gasco, Thymopentin in solid lipid nanoparticles, *Int. J. Pharm.*, 1996, **132**(1), 259–261.
 - 160 R. Cavalli, M. R. Gasco, P. Chetoni, S. Burgalassi and M. F. Saettone, Solid lipid nanoparticles (SLN) as ocular delivery system for tobramycin, *Int. J. Pharm.*, 2002, **238**(1–2), 241–245.
 - 161 M. S. Freag, A. S. Torky, M. M. Nasra, D. A. Abdelmonsif and O. Y. Abdallah, Liquid crystalline nanoreservoir releasing a highly skin-penetrating berberine oleate complex for psoriasis management, *Nanomedicine*, 2019, **14**(8), 931–954.
 - 162 S. Sun, N. Liang, H. Yamamoto, Y. Kawashima, F. Cui and P. Yan, pH-sensitive poly(lactide-co-glycolide) nanoparticle composite microcapsules for oral delivery of insulin, *Int. J. Nanomed.*, 2015, **10**, 3489–3498.
 - 163 H. Zhao, H. Lu, T. Gong and Z. Zhang, Nanoemulsion loaded with l-cystine-oleic acid ionic complex: physicochemical characteristics, in vitro, in vivo evaluation, and antitumor activity, *Int. J. Nanomed.*, 2013, **8**, 1959–1973.
 - 164 T. Zhang, Y. Zheng, Q. Peng, X. Cao, T. Gong and Z. Zhang, A novel submicron emulsion system loaded with vincristine-oleic acid ion-pair complex with improved anticancer effect: in vitro and in vivo studies, *Int. J. Nanomed.*, 2013, **8**, 1185–1196.
 - 165 I. Nazir, M. H. Asim, A. Dizdarevic and A. Bernkop-Schnurch, Self-emulsifying drug delivery systems: Impact of stability of hydrophobic ion pairs on drug release, *Int. J. Pharm.*, 2019, **561**, 197–205.
 - 166 N. Mittapelly, M. Thalla, G. Pandey, V. T. Banala, S. Sharma, A. Arya, S. Mishra, K. Mitra, S. Shukla and P. R. Mishra, Long Acting Ionically Paired Embonate Based Nanocrystals of Donepezil for the Treatment of Alzheimer's Disease: a Proof of Concept Study, *Pharm. Res.*, 2017, **34**(11), 2322–2335.
 - 167 S. J. Novick and J. S. Dordick, Protein-containing hydrophobic coatings and films, *Biomaterials*, 2002, **23**(2), 441–448.
 - 168 L. Battaglia, M. Gallarate, E. Peira, D. Chirio, I. Solazzi, S. Marzia Adele Giordano, C. Gigliotti, C. Riganti and C. Dianzani, Bevacizumab loaded solid lipid nanoparticles prepared by the coacervation technique: Preliminary in vitro studies. 2015, vol. 26, p. 255102.
 - 169 N. Lupo, V. N. Tkadlečková, M. Jelkmann, F. Laffleur, G. Hetényi, K. Kubová and A. Bernkop-Schnürch, Self-emulsifying drug delivery systems: In vivo evaluation of their potential for oral vaccination, *Acta Biomater.*, 2019.
 - 170 J. Griesser, G. Hetenyi, H. Kadas, F. Demarne, V. Jannin and A. Bernkop-Schnurch, Self-emulsifying peptide drug delivery systems: How to make them highly mucus permeating, *Int. J. Pharm.*, 2018, **538**(1–2), 159–166.
 - 171 R. Falk and T. W. Randolph, *Process Variable Implications for Residual Solvent Removal and Polymer Morphology in the Formation of Gentamycin-Loaded Poly (L-lactide) Microparticles*. 1998; vol. 15, pp. 1233–7.
 - 172 R. Alcock, J. A. Blair, D. J. O'Mahony, A. Raoof and A. V. Quirk, Modifying the release of leuprolide from spray dried OED microparticles, *J. Controlled Release*, 2002, **82**(2–3), 429–440.
 - 173 A. D. Holmkvist, A. Friberg, U. J. Nilsson and J. Schouenborg, Hydrophobic ion pairing of a minocycline/Ca²⁺/AOT complex for preparation of drug-loaded PLGA nanoparticles with improved sustained release, *Int. J. Pharm.*, 2016, **499**(1), 351–357.
 - 174 J. T. Evans, J. R. Ward, J. Kern and M. E. Johnson, A single vaccination with protein-microspheres elicits a strong CD8 T-cell-mediated immune response against Mycobacterium tuberculosis antigen Mtb8.4, *Vaccine*, 2004, **22**(15–16), 1964–1972.
 - 175 M. Hill, R. N. Cunningham, R. M. Hathout, C. Johnston, J. G. Hardy and M. E. Migaud, Formulation of Antimicrobial Tobramycin Loaded PLGA Nanoparticles via Complexation with AOT, *J. Funct. Biomater.*, 2019, **10**(2), 26.
 - 176 N. A. Efiana, A. Dizdarevic, C. W. Huck and A. Bernkop-Schnurch, Improved intestinal mucus permeation of vancomycin via incorporation into nanocarrier containing papain-palmitate, *J. Pharm. Sci.*, 2019.
 - 177 K. Shi, F. Cui, H. Yamamoto and Y. Kawashima, Optimized preparation of insulin-lauryl sulfate complex loaded poly (lactide-co-glycolide) nanoparticles using response surface methodology, *Pharmazie*, 2008, **63**(10), 721–725.
 - 178 K. Shi, F. Cui, H. Yamamoto and Y. Kawashima, Optimized formulation of high-payload PLGA nanoparticles containing insulin-lauryl sulfate complex, *Drug Dev. Ind. Pharm.*, 2009, **35**(2), 177–184.
 - 179 H. Zhou, Y. Zhang, D. L. Biggs, M. C. Manning, T. W. Randolph, U. Christians, B. M. Hybertson and K. Y. Ng, Microparticle-based lung delivery of INH decreases INH metabolism and targets alveolar macrophages, *J. Controlled Release*, 2005, **107**(2), 288–299.

