

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Mater. Adv.*, 2020,
1, 2846Structure dependent photostability of ITIC
and ITIC-4F[†]Laura Ciammaruchi,^{ID} ^{*a} Osnat Zapata-Arteaga,^a Edgar Gutiérrez-Fernández,^b
Jaime Martín^{ID} ^{bc} and Mariano Campoy-Quiles^{ID} ^{*a}

Strong synthetic and engineering efforts have taken the efficiency of non-fullerene acceptor (NFA) based organic solar cells above 18% in a few years. Nonetheless, a deep understanding of the fundamental properties of this class of molecules is still missing. Here, we systematically investigated the morphological properties of two high efficient indacenodithienothiophene-based NFAs – namely ITIC and ITIC-4F – in order to correlate the hydrogen/fluorination substitutions with the materials structural and stability properties. We confirm that each NFA structurally evolves with increasing temperature into several polymorphs, identifying through spectroscopy their corresponding narrow temperature ranges. We demonstrate that the materials' response to accelerated stress tests (ASTs) is both substitution and polymorph dependent. ASTs underlined that the most vulnerable molecular segment corresponds to the thienothiophene C=C bond along the central backbone, together with the C=C linkage between the electron-rich donor and the electron-deficient acceptor moieties, with a degradation process triggered by oxygen and light. ITIC-4F showed lower oxidation capability and a higher bond strength retaining effect compared to ITIC. Lastly, the AST approach employed here allowed for the extrapolation of morphological and stability-related features within a high-throughput framework, and can be considered as a valuable methodological tool for future stability-related studies.

Received 26th June 2020,
Accepted 1st October 2020

DOI: 10.1039/d0ma00458h

rsc.li/materials-advances

Introduction

Last decade has witnessed the potential of organic photovoltaics (OPV) as an efficient, lightweight, flexible, and semi-transparent solar technology fabricated through a series of low-cost processes^{1–3} – like deposition from solution by printing and/or coating techniques – which could replace standard and costly vacuum-based fabrication processes. These advantages come from the unique characteristics of the organic semiconductors used as the photoactive layer (PAL), typically being a conjugated electron-donor polymer or small molecule, in combination with a molecule based either on fullerene acceptors (FAs) or non-fullerene acceptors (NFAs). The latter, showing a broader solar absorption spectrum and the possibility to finely tune their energy levels, have allowed to break the 18% power conversion efficiency (PCE) benchmark for an OPV in ternary configuration.⁴ Morphology is a key parameter strongly

influencing the OPV performance and stability, and due to the huge variety of existing NFAs, rather differing conclusions are being drawn at present, in terms of its impact on the device efficiency. In addition, record efficiencies of NFA-based OPV and an in-depth understanding of the basic properties related to such high-efficiency materials, barely go hand in hand. As an example, Ye *et al.*⁵ demonstrated that solvent additives like 1,8-diiodooctane (DIO), together with thermal treatments, would improve the NFA-based blend multilength scale morphology and induce a higher degree of molecular ordering and crystallinity, with a resultant high-efficiency OPV. Nevertheless, as a lesson learned from the fullerene-based OPV world, it is now well known that DIO leads to an accelerated device degradation.^{6,7} Therefore, an in-depth understanding of the basic morphological properties related to such novel highly efficient acceptors, and how these can ultimately impact the device efficiency and stability, seems essential.

Among the most high-efficiency NFAs, indacenodithienothiophene (IDTT)-based ITIC (2,2'-[[6,6,12,12-tetrakis(4-hexylphenyl)-6,12-dihydrodithieno[2,3-d':2',3'-d']-s-indaceno[1,2-b:5,6-b']dithiophene-2,8-diyl]-bis[methyldiylidene(3-oxo-1*H*-indene-2,1(3*H*)-diylidene)]]bis[propanedinitrile]) was first synthesized in 2015,⁸ and since then many ITIC derivatives were designed, achieving PCEs steadily growing over time.^{9–11} ITIC acceptor belongs to the family of acceptor–donor–acceptor (A–D–A)-type

^a Institute of Materials Science of Barcelona (ICMAB-CSIC), Campus of the UAB, 08193, Bellaterra, Spain. E-mail: lciammaruchi@icmab.es, mcampoy@icmab.es^b POLYMAT and Polymer Science and Technology Department, Faculty of Chemistry, University of the Basque Country UPV/EHU, Manuel de Lardizabal 3, 20018, Donostia – San Sebastián, Spain^c Ikerbasque, Basque Foundation for Science, E-48011, Bilbao, Spain[†] Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ma00458h



Fig. 1 Characterization of as-cast NFAs. Absorption (filled symbols) and PL (unfilled symbols) spectra of ITIC (square) and ITIC-4F (circle) (a). Normalized experimental as-cast (solid lines) and DFT-calculated (dotted lines) ITIC (top 2) and ITIC-4F (bottom 2) spectra (b). Peaks and main vibrational modes assignments are discussed in the main text, and are guided by DFT simulations as well as comparison with the literature. GIXWAXS 2D patterns and 1D in-plane and out-of-plane profiles for as-cast ITIC (c and d) and ITIC-4F (e and f).

small molecules, in which a donor core, comprising aromatic fused rings with extended conjugation, is connected to the sides to electron-deficient end groups, which favor the intermolecular π - π overlap and enhance the carrier mobility (Fig. 1b, inset).

One of the most remarkable ITIC derivatives is the tetra-fluorinated ITIC-4F, in which the end-group 2-(3-oxo-2,3-dihydro-1H-inden-1-ylidene) malononitrile (INCN) is symmetrically fluorine-substituted (Fig. 1b inset, X=F). By enhancing the fluorination density, both the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO) levels are pulled down simultaneously. While fluorination decreases the open-circuit voltage (V_{OC}), it also induces an enhancement in the short-circuit current (J_{SC}) by contracting the NFA optical bandgap, therefore compensating for the V_{OC} loss.^{12–14} Fluorine addition also showed to improve the acceptor's inter- and intra-molecular interactions. As well, inclusion of new moieties at the ITIC end-groups can significantly change its temperature-dependent morphology and crystallinity.¹⁵

Since thermal treatments are some of the essential processes related to OPV fabrication, a proper knowledge of the relationship between ITIC fluorination and its temperature-dependent structural and optical properties becomes crucial.

While new NFA materials are constantly being designed,^{16,17} the majority of research groups is mostly focused on the search for the best achievable efficiencies. Top performing but unsuitable (*i.e.* unstable) materials would, however, not make for a good “real” solar device. In this respect, whereas the scientific problem related to the stability and degradation of standard (fullerene-based) OPV has opened up specific research pathways and is being steadily tackled,^{18–21} the same debate is starting to arise only now around NFA-based OPV. Interestingly, some disagreement is emerging on whether NFA-based OPVs show worse or better stability compared to their fullerene-based counterparts, and on which is the most relevant factor triggering instability. (Part of such discrepancy could likely come from the quite different testing conditions applied by each research group.)



Zhao *et al.*²² reported joint superior efficiency and thermal stability for OPVs based on PBDB-T poly[(2,6-(4,8-bis(5-(2-ethylhexyl)-thiophen-2-yl)-benzo[1,2-*b*:4,5-*b'*]dithiophene))-*alt*-(5,5-(1',3'-di-2-thienyl-5',7'-bis(2-ethylhexyl)benzo[1',2'-*c*:4',5'-*c'*]dithiophene-4,8-dione))] donor and ITIC acceptor, compared to the PBDB-T:PCBM-based counterpart. In contrast, Brabec's group²³ showed only similar photoconversion efficiency (PCE) aging trends for PCBM- and for two specific ITIC derivatives- (*i.e.* fluorine and thiophene substituted ITIC) based cells, owing to the lack of conjugation breaking of the latter upon light soaking. These authors explained the poorer photostability results of the other ITIC derivative-based OPVs tested (ITIC, ITIC-M) in view of the increased number of energetic traps generated upon the NFA reorientation. In parallel, also Nutifafa *et al.*²⁴ demonstrated the higher photostability of PCBM-based devices over the ITIC-based ones. Nevertheless, they discarded a trap-assisted recombination as the main reason behind the observed photo-degradation, instead a mobility loss upon light exposure was identified as the main contributor to the difference in the OPV photodegradation. In any case, the NFA blending with a donor polymer seems to slow-down/alter the degradation pathway of the bare NFA. ITIC-based OPV instability under light soaking was additionally verified by Park and Son,²⁵ but in this case the NFA/zinc oxide interface was identified as the most chemically vulnerable cell's portion, and the need for stable aromatic structures was underlined in order to achieve an acceptable device stability. In the same spirit, Guo *et al.*²⁶ proved that introducing stabilizers, like nickel chelate S6, would improve the photo-oxidation stability of many NFAs. Whereas the environmental molecules interaction with NFAs can be mitigated with the introduction of anti-oxidants, Kim's group²⁷ investigated how the molecular structure of two different NFAs, *i.e.* o-IDTBR and IDFBF, could influence their photostability in air. They found a three-phase process for which light and ambient contact triggered an initial conformational change, followed by fragmentation and chromophore disruption, lastly closed by a complete photo-bleaching. Interestingly, the less planar IDFBF showed worse degradation rate with respect to the more crystalline o-IDTBR.

From the literature results presented above it is apparent that there is a lack of general understanding of the stability at the material and device level. A more fundamental understanding of the interaction between the bare NFA morphology and its chemical structure (specific for each NFA family) with its stability under light and/or air, would surely help to disentangle the different instability sources at the device level. Therefore, in here we report a study on thin films of two NFAs, namely ITIC and ITIC-4F, investigated using photoluminescence (PL), absorption and Raman scattering. First we evaluate the annealing temperature effect on the structural and optical properties of the two materials, comparing the influence of fluorination on the type of polymorph as well as on the phase transition temperatures. Moreover, we discuss how the specific end-group substitution affects stability of the NFA polymorphic states, in response to conditions of accelerated stress tests (ASTs). We find that the photostability of ITIC is markedly dependent on

the specific polymorphic phase and the fluorine decoration. Fluorination is able to slow down the molecule degradation induced *via* AST, likely due to a stronger chemical stability inducing a retaining effect. Finally, we point out that this study has been carried out by introducing annealing temperature gradients within the very same samples, thus we assess the NFA morphological characteristics – as well as the AST effects on them – in a high-throughput screening fashion. The advantage of this approach in stability studies is two-fold, as it allows for a significant saving of lab time and material use.^{19,28–30}

Experimental section

Materials

ITIC and ITIC-4F acceptors were purchased from 1-Material, ZnO nanoparticles dispersion was acquired from Avantama, while indium tin oxide (ITO)-covered substrates were purchased from Ossila.

Samples preparation

In order to produce an as realistic as possible PV interphase, a uniform ZnO layer was blade coated on the ITO-substrate, before the NFA deposition. ZnO blade coating was performed in air, using an automatic Zehntner ZAA 2300 with an aluminum applicator Zehntner ZUA 2000.²⁹ After the deposition, samples were annealed in ambient conditions at 105 °C for 30 minutes. Both acceptors were dissolved in chlorobenzene (CB) in a concentration of ~13 mg mL⁻¹. After an overnight stirring at 80 °C and 1000 rpm, the acceptor materials were blade coated inside a nitrogen-filled and dry glove box, using a second blade coater equipment of similar brand and model, kept at 80 °C. According to the selected conditions of speed (70 mm s⁻¹) and blade gap (200 μm), we obtained films roughly 70 nm thick. After deposition, NFA-covered samples were thermally annealed inside the same glove box for 30 minutes within the range (90–250 °C), using a calibrated Kofler bench (Wagner & Munz). This type of hot stage produces a controlled temperature gradient which is then transferred to the sample, enabling the production of films with a lateral thermal annealing gradient.²⁸

Characterization

UV-vis absorption spectra were recorded using a Hitachi U-3000 spectrophotometer. Optical microscopy images were obtained using an OPTIKA B-600 MET microscope in crossed polarizer configuration. Raman scattering and PL signals were acquired using a WITec alpha 300 RA+ confocal Raman setup, coupled to an Olympus objective with 10× magnification. 488 nm and 633 nm centered lasers were employed for Raman and PL measurements, respectively. For The 488 nm-based AST on annealed samples, several measurements at different powers were performed on nominally similar samples, in order to plot the Raman features evolution against the dose. The laser powers used were 0.25 mW, 0.50 mW, 0.75 mW, 1 mW, and 1.5 mW. For 633 nm-based PL measurements, we fixed the power to 0.25 mW. All raw data were collected and treated using



Table 1 Assignment of main ITICs Raman peaks in the range 1300–1700 cm⁻¹

Raman shift (cm ⁻¹)	Assignment (main vibration)
~ 1345 (α)	C-C & C-H (INCN group)
~ 1440 (β)	C=C (thiophene) C=C (alkenes) C-H linkage (IDTT and INCN)
~ 1490 (γ)	C-H central ring
~ 1550 (δ)	C=C (IDTT central benzene)
~ 1600 (ϵ)	C=C (phenyl INCN)
~ 1705 (ζ)	C=N linkage (INCN)

optical and vibrational features, we wanted to understand how fluorination would influence the NFA stability. For this, we first performed *in situ* photodegradation of as-cast ITICs thin-films, using the lasers' excitations as a way to accelerate the degradation process. The experimental setup we used allowed us to collect real-time Raman and PL signals as a function of the laser irradiation time.²⁷

We used a monochromatic 488 nm (Raman) and 633 nm (PL) lasers to perform AST with power densities between two and three orders of magnitude higher than the standard AM1.5G (details in Experimental section). Fig. 2a depicts the integrated PL intensity dependence of as-cast ITICs upon degradation time. In the inset, the spectral evolution of normalized PL spectra selected at specific degradation points, is represented.

Both materials show heavy PL quenching over time, with ITIC-4F displaying a slight red-shift over the annealing time (from 785 nm to 793 nm). With increasing illumination time, the main peaks Raman intensity signal decreases (Fig. 2b, taken at 0.5 mW), suggesting a chromophore loss during the photo-oxidation process.

The PL quenching intensity has a direct relationship with the density of quenching sites³³ and for samples measured in ambient, air photo-oxidation is known to induce a rapid increase of such density.³⁴ In fact, active radicals can be often formed as a result of photosensitization in the presence of oxygen, metal catalysts (ITO/ZnO) and other residues^{25,35,36}

Results and discussion

Characterization of as-cast ITICs

Thin films of NFAs were deposited by blade coating on ZnO/ITO substrates (see experimental section for details). The as-cast films were first characterized by UV-visible optical absorption, PL and Raman spectroscopy techniques, and representative spectra of both ITIC and ITIC-4F are shown in Fig. 1. UV-vis spectra (Fig. 1a) of both ITICs exhibit a stronger 0-0 transition at higher wavelengths and a less intense 0-1 transition at shorter wavelengths. Fluorine substitution in the INCN end group enhances the electron push-pull effect, and is the origin of the slightly red-shifted UV-vis absorption and PL emission onsets compared to the non-fluorinated ITIC (Fig. 1a). On the other hand, experimental Raman spectra (Fig. 1b) of both ITIC types show a general match in their main vibrational modes. In fact, the fluorine substitution in the ITIC end group – which should correspond to a C-F Raman spectral feature falling between 500 cm^{-1} and 800 cm^{-1} – could be detected only by using laser powers of $\sim 200\text{ mW}$, *i.e.* at least two order of magnitude higher than the maximum one employed in this work.^{31,32} We used DFT simulations (Fig. 1b, dashed) to assign the six strongest vibration modes falling between 1300 cm^{-1} and 1700 cm^{-1} at different molecular sites. For detailed assignment see Table 1.

Two-dimensional Grazing Incidence Wide Angle X-ray Scattering (2D GIWAXS) patterns for both as-cast ITICs (Fig. 1c-f) show poor molecular order, suggesting largely low-crystalline structures. Narrow peaks near $Q = 20 \text{ nm}^{-1}$ come from the silicon substrate scattering.

AST on as-cast ITICs

Having realized the initial characterization of both fluorinated and non-fluorinated ITICs in terms of their main structural,

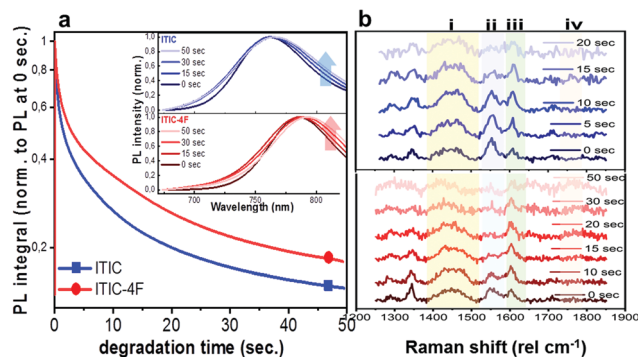


Fig. 2 AST on as-cast ITICs. *In situ* integrated PL intensity decay of as-cast ITIC (square) and ITIC-4F (circle) upon 633 nm laser excitation. Inset: Normalized PL spectra taken at different degradation times, for as-cast ITIC (upper panel) and ITIC-4F (lower panel) (a). *In situ* Raman spectra of as-cast ITIC (upper panel) and ITIC-4F (lower panel), corresponding to different degradation times upon 488 nm excitation (b).

This journal is © The Royal Society of Chemistry 2020



Fig. 3 Detailed Raman analysis of peaks evolution upon AST. Normalized integrated intensity of i (1450 cm^{-1}), ii (1550 cm^{-1}), iii (1600 cm^{-1}) and iv (1750 cm^{-1}) Raman peaks, extracted from Raman time series plots as a function of dose, for as-cast ITIC (column a) and ITIC-4F (column b) upon 488 nm excitation.

peak area of this new feature increases almost twice as much for ITIC than for ITIC-4F, confirming the higher oxidation capability of the former under the same degrading conditions. Also, ITIC-4F starts reacting/oxidizing after receiving a slightly higher dose intake, compared to non-fluorinated ITIC, and the overall growth process appears much faster for ITIC than for ITIC-4F. Due to the same mechanism, we also explain the almost doubled times for the ITIC-4F Raman modes to reach the same degradation level upon similar dose amounts received, with respect to ITIC (Fig. 3a and b, i–iii).

It has been recently shown⁵³ that, when ITIC is put in a basic environment, OH^- anions can react as nucleophiles and attack the linkage between D and A moieties of the NFA, with the direct consequence of a conjugation break and the alteration of the charge transfer properties of the chain. These results provide extra proof of the ITIC molecule weakness mostly localized in the $\text{C}=\text{C}$ linkage between D and A groups. In the same work, Zhu *et al.* also verified that while the photovoltaic performances of OH^- added ITIC devices hugely dropped compared to the OH^- free reference – with short circuit current (J_{sc}) and



endorses this explanation, as a lower (higher) level of inter-chain coupling would correspond to a less (more) ordered crystalline structure, resulting in a higher (lower) A_{0-0}/A_{0-1} value.^{57,58}

Annealing both ITICs at $T \geq T_g$ produces further conformational changes, reflected by the appearance of specific absorption features, as revealed in Fig. 4a, b and 5a, b. In more detail, when ITIC is annealed at temperatures between 180 °C and 230 °C, the A_{0-0} peak intensity increases (Fig. 4a) most probably due to the formation of a different polymorph (phase II). The further raise of the temperature (to 230–250 °C) results in the quick drop of the A_{0-0} peak intensity, due to a further transition into a phase III polymorph. On the other side, the A_{0-0} peak shift (Fig. 5a) undergoes a marked blue-shift (~ 20 nm) in the phase II temperature region, followed by a back red-shift for phase III. Therefore, ITIC passes through an intermediate phase (polymorph II¹⁵) in which the combination of A_{0-0} blue shift together with its increased A_{0-0}/A_{0-1} ratio, indicates that the crystallization process evolves through a temporary shorter conjugation-length. Such conjugation seems to be recovered for $T > 230$ °C. Indeed, it has been reported that for ideal H(J)-aggregates, increasing disorder (180–230 °C region in our experiments) leads to an increase (decrease) in the vibronic A_{0-0}/A_{0-1} intensity ratio.⁵⁹

Nevertheless, in a molecular π -stack a competition always exists between interchain (H-like) and intrachain (J-like) interactions, and some crossover from H- to J-aggregate behavior can easily show up.⁵⁸ Unlike ITIC, ITIC-4F A_{0-0} peak shows a strong red-shift when crossing its T_g (~ 170 °C), an indication that the small molecule might be acquiring stronger conjugation along the backbone with increased temperature. A closer look at the ITIC-4F A_{0-0}/A_{0-1} peak ratio reveals that such phase change is accompanied by a transitory increased disorder, briefly showing up between 180 °C and 200 °C. GIWAXS measurements for materials annealed at 200 °C show more in-plane crystallinity features for ITIC-4F, than ITIC (Fig. 6 and 7e, f). The ITIC-4F phase transformation seems to happen in a much smaller temperature window, compared to ITIC. T_a -dependent PL contour plots (Fig. 4c) and PL peak shifts (Fig. 5c) confirm the presence of distinct polymorphic phases, while GIWAXS patterns (Fig. 6 and Fig. 7a, c, e) and scattering profiles (Fig. 6 and 7b, d, f) reveal the different level of crystallinity associated to them. Note that the use of temperature dependent PL measurements has been successfully used to probe the signatures of thermal transitions in conjugated polymers.⁶⁰

To further understand the effect of fluorine substitution on the ITIC temperature-dependent molecular order, we measured Raman spectra under 488 nm excitation. Fig. 4e and f show the complete normalized Raman spectra of ITIC and ITIC-4F at different T_a , while in Fig. 5e and f the detail of the four main vibrational modes, in the range 1300 cm^{-1} – 1700 cm^{-1} , is reported. Since – in very broad terms – the Raman signal is based on the interaction between the material’s electronic cloud and the external electric field induced by the measurement laser light,^{61,62} a general look at Fig. 5e and f already suggests that ITIC-4F may retain its structural features through

This journal is © The Royal Society of Chemistry 2020




Fig. 4 UV-vis, PL and Raman evolution upon materials annealing. Phase-dependent ITIC (left column) and ITIC-4F (right column) UV-vis absorption contour maps (top row, a and b), PL contour maps (middle row, c and d) and normalized Raman spectra (bottom row, e and f) as function of the annealing temperature. Four regions are identified in the contour maps for each NFA, according to their polymorphic phase. All measurements were realized at room temperature, after the materials underwent annealing and subsequent cool-down in inert atmosphere.

a wider annealing temperature range, as compared to ITIC. Indeed, the ITIC-4F C–C intraring (in-plane skeleton) stretch modes ($\sim 1340\text{ cm}^{-1}$, 1) position and intensity seem more unaffected by the specific phase than those of ITIC. On the other hand, the peak at $\sim 1600\text{ cm}^{-1}$ (4) assigned to the end-group fused phenyl ring,⁶³ shows a higher variability for ITIC than for ITIC-4F. NFA end-groups have been identified as the ones responsible to create charge transport channels *via* end-group interactions between different molecules.^{64–66} Therefore, depending on their planarity and π – π stacking, they could either facilitate – or hinder – such intermolecular interactions and the charge transport across neighboring molecules.⁶⁷ π – π stacking values of $\sim 3.5\text{ \AA}$ and $3.35\text{ \AA}$ have been recently reported for ITIC⁶⁷ and ITIF-4F,⁴⁷ respectively. Therefore, these

results seem to suggest that fluorination, favoring a higher molecular planarization and closer packing – likely *via* the formation of the intramolecular noncovalent interactions^{38,47} – could grant higher molecular stiffness toward annealing temperature, with respect to ITIC. While peaks 2 and 3 (Fig. 5e and f) are commonly associated to collective C=C bond stretching modes of the conjugated molecule backbone, based on DFT calculation and literature reports^{68–70} we could distinguish and assign the $\sim 1450\text{ cm}^{-1}$ vibrations (2) mostly to the thiophene-related C=C stretching mode, while the $\sim 1550\text{ cm}^{-1}$ (3) to the C=C central ring stretching mode. The biggest shape change registered for ITIC happens at the C=C stretch peak ($\sim 1450\text{ cm}^{-1}$) for $T > 200\text{ }^{\circ}\text{C}$, when a well pronounced shoulder at $\sim 1420\text{ cm}^{-1}$ appears, whose presence has been





Having established a relationship between T_a and the structural features of fluorinated *vs.* non fluorinated ITIC - *i.e.* their



Fig. 6 GIWAXS 2D patterns (a, c and e) and 1D in-plane and out-of-plane profiles (b, d and f) for ITIC annealed at different temperatures.

thermal transition temperatures and how these may affect their molecular bonding – we next study the NFA stability in thermally annealed materials. In fact, thermal treatments are among the most fundamental fabrication steps of a solar cell throughout the entire production process. For this, investigating not just the as cast-, but also the polymorphic phase-dependent ITICs stability becomes especially relevant in order to simultaneously achieve efficient and durable solar devices. Therefore, we screened the different polymorphic ITICs phases under similar accelerated degrading conditions. Fig. 8a and b report the log-log integrated PL decay of the 4 ITICs structural phases as a function of the degrading time; Fig. 8c and d show the semi-log degrading trends of Raman peak i, against the dose intake (peaks ii and iii displayed in Fig. S3, ESI†). First, we notice that PL and Raman measurements coherently verify that stability depends on the specific NFA investigated. In detail, ITIC shows its least stable regimes below T_g , while its most stable polymorph appears for $T_a > 200$ °C (phases II and III).

From the Raman measurements, we also determine that among phases II and III, the longest lasting integrated Raman peak i signal comes from phase III, when – in agreement with results from Martin's group¹⁵ – the material reaches its lowest free energy, and presumably its highest thermodynamical stability. The relative stability of ITIC-4F polymorphs instead, does not seem to correlate directly with the order of the material's crystallization phases. In fact, unlike ITIC, the highest annealing temperature (~ 230 °C, phase III) for ITIC-4F does not bring the material to the most stable phase, but rather the opposite.

It is worth noting that the integrated [630–650 nm] absorption range plotted against T_a (Fig. S4, ESI†) proves that the observed stability variation between phases is not an artifact associated to different phases having different absorption coefficients, which would in turn vary the total absorbed 633 nm laser power. ITIC-4F Raman peak i signal for phases I and III show the quickest intensity drops. Yet, slight differences in the degradation time scales between PL and Raman might be



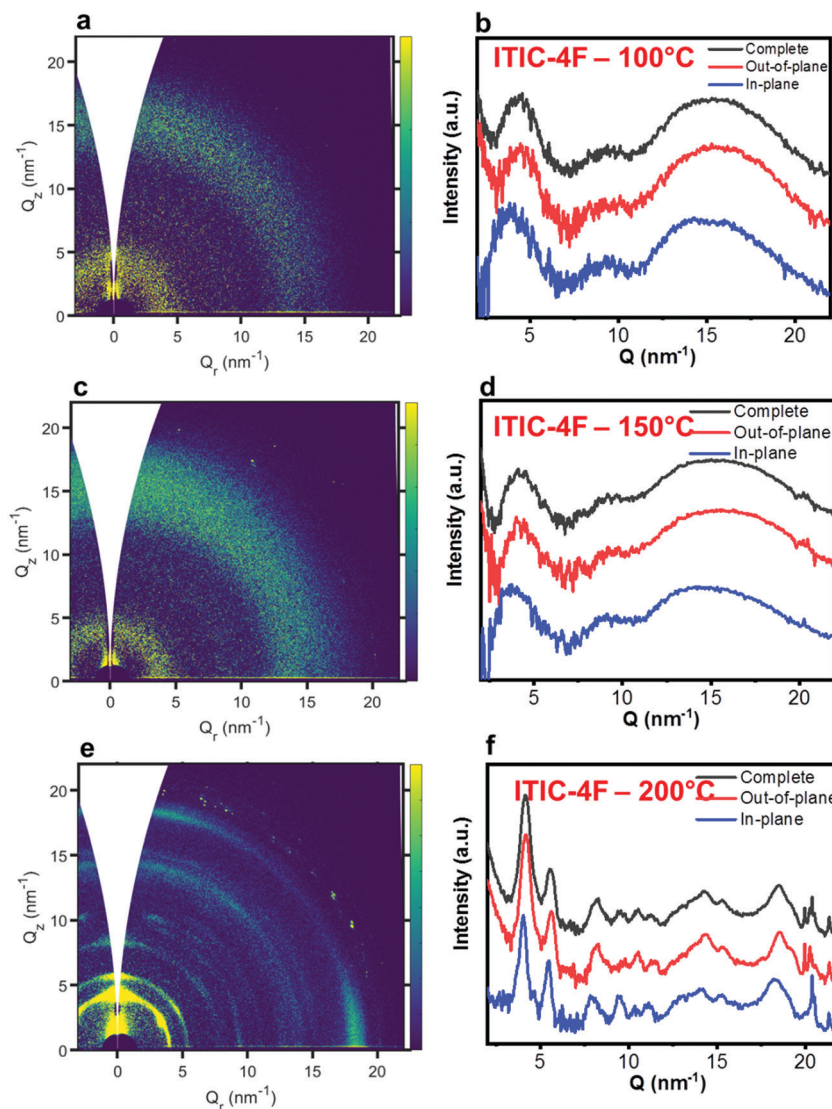


Fig. 7 GIWAXS 2D patterns (a, c and e) and 1D in-plane and out-of-plane profiles (b, d and f) for ITIC-4F annealed at different temperatures.

Table 2 Main ITICs crystallinity features according to the applied annealing temperatures

	Phase	T range (°C)	Crystallinity features (aggregate type)
ITIC	I*	RT to ~140	Loose crystallinity (HJ-type)
	I**	~140 to ~180	Beginning of crystallization process (towards more J-type)
	II	~180 to ~230	Conjugation loss (more H-type)
	III	~230 to ~250	More ordered phase (more J-type)
ITIC-4F	I*	RT to ~130	Loose crystallinity (HJ-type)
	I**	~130 to ~170	Beginning of crystallization process (towards more J-type)
	II	~170 to ~220	A large crystallinity is acquired (strong J-like character)
	III	~220 to ~250	Crystallinity reduces

due to the different illumination laser wavelengths used to perform the AST and collect the signals.

In order to further prove the oxidative cleavage of the alkenes-based units as the major trigger for the degradation process of ITIC-based NFAs – as well as to check whether different phases would differently respond to the AST – we repeated similar *in situ* degradation experiments on annealed

and encapsulated samples. Fig. 8e and f show Raman peak i results relative to ITIC (Fig. 8e) and ITIC-4F (Fig. 8f) annealed at 200 °C (Raman peak ii and iii results for samples annealed at 200 °C, as well as Raman peaks i–iii results for samples annealed at 150 °C reported in Fig. S5 and S6, ESI†). Our results make clear that in the absence of oxygen (and water), the degradation process of both NFAs experiences a huge delay.



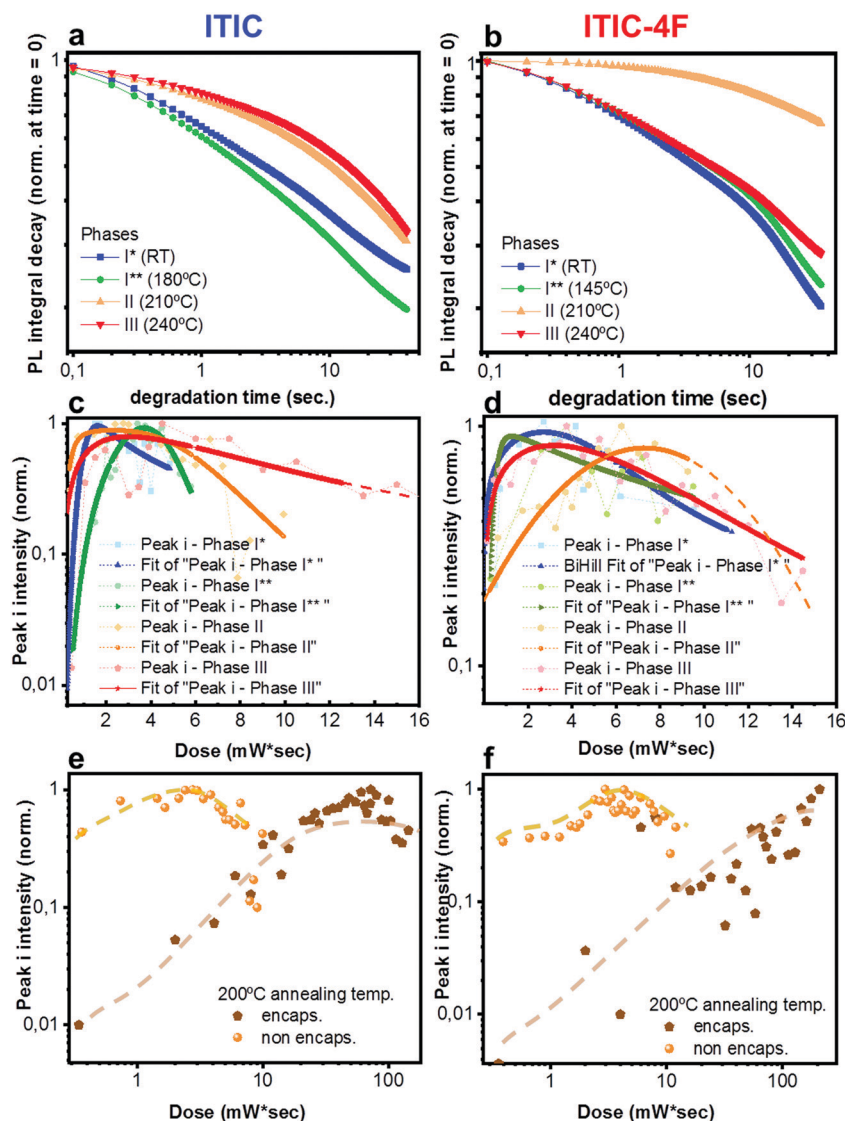


Fig. 8 *In situ* integrated PL intensity decay of ITIC (a) and ITIC-4F (b) in their different polymorphic phases (I^* ~ RT, I^{**} ~ 180 °C for ITIC and 150° for ITIC-4F, II ~ 210 °C, III ~ 240 °C) upon 633 nm laser excitation, as a function of degradation time. Normalized integrated Raman intensity of peak i ($(1450) \text{ cm}^{-1}$) as a function of dose for non-encapsulated ITIC (c) and ITIC-4F (d) in their different polymorphic states, upon 488 nm excitation. Normalized integrated Raman intensity of peak i ($(1450) \text{ cm}^{-1}$) as a function of dose for encapsulated ITIC (e) and ITIC-4F (f) annealed at 200 °C, upon 488 nm excitation. Results for non-encapsulated ITICs are also reported for comparison. Dashed lines are only a guide for the eye.

It is also clear that the formation of free radicals, responsible for initiating the autoxidation cycle, is jointly triggered by light. But while ITIC starts to drop in intensity for a dose intake of *ca.* 80 mW s, ITIC-4F peak i intensity does not show signs of decrease even after a dose intake as high as 110 mW s.

Lastly, PL intensity profiles of T_a -dependent ITICs degraded under 633 nm laser could be accurately fitted using decreasing exponential functions (Fig. S8 and S9, ESI† for fitting equations). The identified trends point at the presence of two main radiative recombination channels in the materials, with the first one (k_1 , cross +) being preminent over the second one (k_2 , tilted cross ×) (Fig. 9). Yet, a closer look at Fig. 9 reveals that, whilst for ITIC-4F (Fig. 9b) k_1 and k_2 follow the same profile throughout the temperature range – with zones of higher and lower decay rates

dependent on the T_a in accordance with the material's response to AST (Fig. 8b) – for ITIC this is not the case. Indeed, while the k_1 decay rate shows a drop in the (125–155 °C) annealing region, the second radiative channel k_2 shows an increase, even though slight, as if in this region the material underwent a structural transition which could temporarily open up local recombination pathways.

Such structural rearrangements in the T_a range 130–150 °C was also detected by Yu *et al.*,⁵⁶ using FSC analysis on annealed ITIC. According to the extrapolated decay rate coefficients of Fig. 9, we see that in the temperature region below T_g each material shows a decay rate minimum, associated to a highly stable phase. The degradation rate upturn shown right before each T_g instead, seems to be likely due to a local amorphization



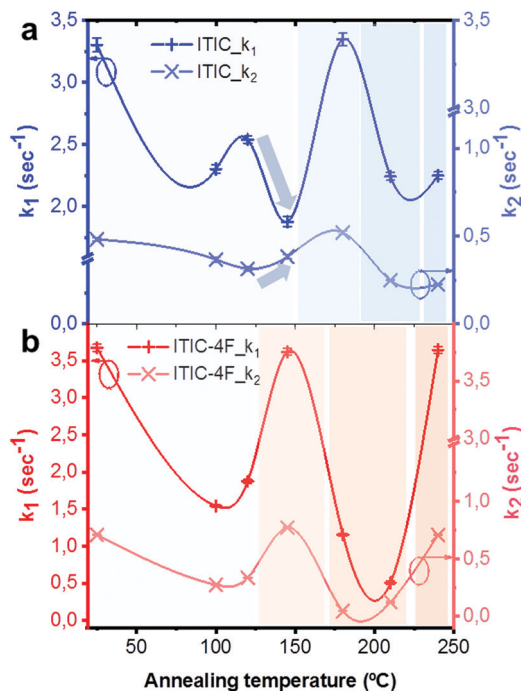


Fig. 9 Decay rates k_1 and k_2 extrapolated from the bi-exponential fitting of ITIC (a) and ITIC-4F (b) PL quenching profiles upon 633 nm laser irradiation, for different annealing temperatures of the materials.

process taking place in the structure.¹⁵ For annealing temperatures well above T_g , the two behaviors markedly differ, as ITIC enters a region of high stability while ITIC-4F evolves toward a region of fewer crystallinity, which in turns affects its stability response. Interestingly, as different isomers of ITIC molecular family may result in different molecular arrangement,⁷³ our polymorph dependent stability suggest that there might be also an isomer-dependent stability, which will be the topic of future investigations.

Conclusions

ITIC and ITIC-4F NFAs were blade-coated and subsequently annealed in the temperature range (90–250 °C). By using several spectroscopic techniques we were able to identify distinct phases with different polymorphs and varying degree of crystallinity, depending on the annealing temperature and the fluorine presence. With the help of DFT calculations, we could infer a relationship between the main NFA molecular bonds, and their T_a dependent morphological evolution.

ASTs were realized with two different monochromatic lasers in order to assess the materials' chemical stability. While C=C of alkene and thiophene based groups showed to be the weakest chemical points for both ITICs, fluorine-substituted NFA displayed a slower the degradation process, likely due to its more favorable energy levels together with its higher degree of order.

Annealed materials were also degraded under 488 nm and 633 nm lasers. For ITIC, we verified that in the temperature

region $T < T_g$, the highest stability to dose intake takes place for $T_a \sim 150$ °C, consistently with literature.⁵⁶ Still, phases II and III for $T_a > T_g$ show the highest stability. For ITIC-4F instead, in the $T < T_g$ range temperatures as low as ~ 120 °C produced the most stable phase against degradation. When passing T_g , the material undergoes a structural evolution marking a phase of high stability (phase II) and a subsequent pretty amorphous one (phase III). While the more stable phases obtained could be associated to higher degree of crystallinity in the NFA materials, this happened at the expense of higher processing temperatures. This may need to be taken into serious consideration, especially when fabricating OPV on flexible substrates. Indeed, usual flexible OPV processing temperatures have to be kept below 150 °C.⁷⁴ Therefore, our findings could serve as an indication of the optimal processing temperature to be used in such ITIC-based solar cells. We will obviously need to verify our hypotheses in a complete OPV device. Degrading annealed and encapsulated samples proved that oxygen is the major trigger of the autoxidation cycle, and that ITIC-4F performs better (*i.e.* degrades less) for both T_a tested (150 °C and 200 °C). Having identified the alkene- and the thiophene-related C=C bonds as the most sensitive molecular portion, we verify that in the fluorine-substituted ITIC, the vinyl moieties are less exposed to oxygen attack and that – depending on the applied annealing temperatures – such bonds may adjust in orientations more or less favorable to external stimuli.

Considering our findings, specific materials and applications could best suit particular processing temperature conditions and fabrication techniques. In this frame, ITIC-based OPVs might be a good choice for delivering high efficiencies, even though their capability of dose intake could be more limited than that of ITIC-4F based ones. On the other hand, ITIC-4F based devices could grant longer-lasting performance. In addition, designing molecules with larger electron affinities, as well as introducing antioxidants that suppress the autoxidation cycle *via* the formation of stable radicals, could be both considered as strategies to make the NFA more robust to radicals' attack. This may result in more intrinsically stable devices. Such accomplishment may loosen, in turn, the present requirements on encapsulation, based on the need to block out oxygen/moisture percolation.^{36,48,75} As a last remark, we note that since OSC performance and stability depend jointly on the NFA morphology and fluorination, the photo-active layer composition (*e.g.* in ternaries blends) and the annealing temperature should be both adjusted, in order to achieve a stable energy output.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to thank Dr Tommaso Salzillo and Dr Valentina Bulova for very fruitful scientific discussions.



- 16 P. Cheng, G. Li, X. Zhan and Y. Yang, *Nat. Photonics*, 2018, **12**, 131–142.
- 17 G. Zhang, J. Zhao, P. C. Y. Chow, K. Jiang, J. Zhang, Z. Zhu, J. Zhang, F. Huang and H. Yan, *Chem. Rev.*, 2018, **118**(7), 3447–3507.
- 18 S. A. Gevorgyan, N. Espinosa, L. Ciammaruchi, B. Roth, F. Livi, S. Tsopanidis, S. Züfle, S. Queirós, A. Gregori, G. A. D. R. Benatto, M. Corazza, M. V. Madsen, M. Hösel, M. J. Beliatas, T. T. Larsen-Olsen, F. Pastorelli, A. Castro, A. Mingorance, V. Lenzi, D. Fluhr, R. Roesch, M. Maria Duarte Ramos, A. Savva, H. Hoppe, L. S. A. Marques, I. Burgués, E. Georgiou, L. Serrano-Luján and F. C. Krebs, *Adv. Energy Mater.*, 2016, **6**(22), 1600910.
- 19 Q. Burlingame, B. Song, L. Ciammaruchi, G. Zanotti, J. Hankett, Z. Chen, E. A. Katz and S. R. Forrest, *Adv. Energy Mater.*, 2016, **6**(21), 1601094.
- 20 L. Ciammaruchi, F. Brunetti and I. Visoly-Fisher, *Sol. Energy*, 2016, **137**, 490–499.
- 21 M. O. Reese, S. A. Gevorgyan, M. Jørgensen, E. Bundgaard, S. R. Kurtz, D. S. Ginley, D. C. Olson, M. T. Lloyd, P. Morvillo, E. A. Katz, A. Elschner, O. Haillant, T. R. Currier, V. Shrotriya, M. Hermenau, M. Riede, K. R. Kirov, G. Trimmel, T. Rath, O. Inganäs, F. Zhang, M. Andersson, K. Tvingstedt, M. Lira-Cantu, D. Laird, C. McGuinness, S. Gowrisanker, M. Pannone, M. Xiao, J. Hauch, R. Steim, D. M. DeLongchamp, R. Rösch, H. Hoppe, N. Espinosa, A. Urbina, G. Yaman-Uzunoglu, J.-B. Bonekamp, A. J. J. M. van Breemen, C. Girotto, E. Voroshazi and F. C. Krebs, *Sol. Energy Mater. Sol. Cells*, 2011, **95**, 1253–1267.
- 22 W. Zhao, D. Qian, S. Zhang, S. Li, O. Inganäs, F. Gao and J. Hou, *Adv. Mater.*, 2016, **28**(23), 4734–4739.
- 23 X. Du, T. Heumueller, W. Gruber, A. Classen, T. Unruh, N. Li and C. J. Brabec, *Joule*, 2019, **3**(1), 215–226.
- 24 N. Y. Doumon, F. V. Houard, J. Dong, H. Yao, G. Portale, J. Hou and L. J. A. Koster, *Org. Electron.*, 2019, **69**, 255–262.
- 25 S. Park and H. J. Son, *J. Mater. Chem. A*, 2019, **7**(45), 25830–25837.
- 26 J. Guo, Y. Wu, R. Sun, W. Wang, J. Guo, Q. Wu, X. Tang, C. Sun, Z. Luo, K. Chang, Z. Zhang, J. Yuan, T. Li, W. Tang, E. Zhou, Z. Xiao, L. Ding, Y. Zou, X. Zhan, C. Yang, Z. Li, C. J. Brabec, Y. Li and J. Min, *J. Mater. Chem. A*, 2019, **7**(43), 25088–25101.
- 27 J. Luke, E. M. Speller, A. Wadsworth, M. F. Wyatt, S. Dimitrov, H. K. H. Lee, Z. Li, W. C. Tsoi, I. McCulloch, D. Bagnis, J. R. Durrant and J. S. Kim, *Adv. Energy Mater.*, 2019, **9**(15), 1803755.
- 28 E. Pascual-San-José, X. Rodríguez-Martínez, R. Adel-Abdelaleim, M. Stella, E. Martínez-Ferrero and M. Campoy-Quiles, *J. Mater. Chem. A*, 2019, **7**(35), 20369–20382.
- 29 A. Harillo-Baños, X. Rodríguez-Martínez and M. Campoy-Quiles, *Adv. Energy Mater.*, 2020, **10**(1), 1902417.
- 30 R. K. Misra, L. Ciammaruchi, S. Aharon, D. Mogilyansky, L. Etgar, I. Visoly-Fisher and E. A. Katz, *ChemSusChem*, 2016, **9**(18), 2572–2577.

- 1 T. R. Andersen, H. F. Dam, M. Hösel, M. Helgesen, J. E. Carlé, T. T. Larsen-Olsen, S. A. Gevorgyan, J. W. Andreasen, J. Adams, N. Li, F. Machui, G. D. Spyropoulos, T. Ameri, N. Lemaître, M. Legros, A. Scheel, D. Gaiser, K. Kreul, S. Berny, O. R. Lozman, S. Nordman, M. Välimäki, M. Vilkmann, R. R. Søndergaard, M. Jørgensen, C. J. Brabec and F. C. Krebs, *Energy Environ. Sci.*, 2014, 7, 2925–2933.
- 2 J. E. Carlé, M. Helgesen, O. Hagemann, M. Hösel, I. M. Heckler, E. Bundgaard, S. A. Gevorgyan, R. R. Søndergaard, M. Jørgensen, R. García-Valverde, S. Chaouki-Almagro, J. A. Villarejo and F. C. Krebs, *Joule*, 2017, 1, 274–289.
- 3 I. Burgués-Ceballos, M. Stella, P. Lacharmoise and E. Martínez-Ferrero, *J. Mater. Chem. A*, 2014, 2, 17711–17722.
- 4 Q. Liu, Y. Jiang, K. Jin, J. Qin, J. Xu, W. Li, J. Xiong, J. Liu, Z. Xiao, K. Sun, S. Yang, X. Zhang and L. Ding, *Sci. Bull.*, 2020, 65(4), 272–275.
- 5 L. Ye, W. Zhao, S. Li, S. Mukherjee, J. H. Carpenter, O. Awartani, X. Jiao, J. Hou and H. Ade, *Adv. Energy Mater.*, 2017, 7, 1602000.
- 6 B. J. Tremolet De Villers, K. A. O'Hara, D. P. Ostrowski, P. H. Biddle, S. E. Shaheen, M. L. Chabini, D. C. Olson and N. Kopidakis, *Chem. Mater.*, 2016, 28(3), 876–884.
- 7 N. Y. Doumon, G. Wang, X. Qiu, A. J. Minnaard, R. C. Chiechi and L. J. A. Koster, *Sci. Rep.*, 2019, 9(1), 1–14.
- 8 Y. Lin, J. Wang, Z. G. Zhang, H. Bai, Y. Li, D. Zhu and X. Zhan, *Adv. Mater.*, 2015, 27(7), 1170–1174.
- 9 C. Yan, S. Barlow, Z. Wang, H. Yan, A. K. Y. Jen, S. R. Marder and X. Zhan, *Nat. Rev. Mater.*, 2018, 3(3), 1–19.
- 10 J. Hou, O. Inganäs, R. H. Friend and F. Gao, *Nat. Mater.*, 2018, 17(2), 119–128.
- 11 A. Wadsworth, M. Moser, A. Marks, M. S. Little, N. Gasparini, C. J. Brabec, D. Baran and I. McCulloch, *Chem. Soc. Rev.*, 2019, 48(6), 1596–1625.
- 12 W. Li, L. Ye, S. Li, H. Yao, H. Ade and J. Hou, *Adv. Mater.*, 2018, 30(16), 1707170.
- 13 Z. Zheng, Q. Hu, S. Zhang, D. Zhang, J. Wang, S. Xie, R. Wang, Y. Qin, W. Li, L. Hong, N. Liang, F. Liu, Y. Zhang, Z. Wei, Z. Tang, T. P. Russell, J. Hou and H. Zhou, *Adv. Mater.*, 2018, 30(34), 1801801.
- 14 W. Zhao, S. Li, H. Yao, S. Zhang, Y. Zhang, B. Yang and J. Hou, *J. Am. Chem. Soc.*, 2017, 139, 7148–7151.
- 15 S. Marina, A. Scaccabarozzi, E. Solano, A. Khirbat, A. Iturrospe, A. Balzer, L. Yu, E. Gabirondo, X. Monnier, T. Anthopoulos, M. Caironi, M. Campoy, C. Müller, D. Cangialosi, N. Stingelin and J. Martin, 2020, unpublished work.

- This journal is © The Royal Society of Chemistry 2020

- 72 C. A. Morgado, J. P. McNamara, I. H. Hillier, N. A. Burton and M. A. Vincent, *J. Chem. Theory Comput.*, 2007, **3**(5), 1656–1664.
- 73 H. Lai, H. Chen, J. Zhou, J. Qu, P. Chao, T. Liu, X. Chang, N. Zheng, Z. Xie and F. He, *iScience*, 2019, **17**, 302–314.
- 74 S. I. Na, Y. H. Seo, Y. C. Nah, S. S. Kim, H. Heo, J. E. Kim, N. Rolston, R. H. Dauskardt, M. Gao, Y. Lee and D. Vak, *Adv. Funct. Mater.*, 2019, **29**(6), 1805825.
- 75 K. U. Ingold and D. A. Pratt, *Chem. Rev.*, 2014, **114**(18), 9022–9046.

