

Cite this: *Chem. Sci.*, 2020, 11, 10744

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Hierarchical nanosheets built from superatomic clusters: properties, exfoliation and single-crystal-to-single-crystal intercalation†

Jonathan A. Kephart,<sup>a</sup> Catherine G. Romero,<sup>a</sup> Chun-Chih Tseng,<sup>b</sup> Kevin J. Anderton,<sup>c</sup> Matthew Yankowitz,<sup>bd</sup> Werner Kaminsky<sup>a</sup> and Alexandra Velian<sup>\*,a</sup>

Tuning the properties of atomic crystals in the two-dimensional (2D) limit is synthetically challenging, but critical to unlock their potential in fundamental research and nanotechnology alike. 2D crystals assembled using superatomic blocks could provide a route to encrypt desirable functionality, yet strategies to link the inorganic blocks together in predetermined dimensionality or symmetry are scarce. Here, we describe the synthesis of anisotropic van der Waals crystalline frameworks using the designer superatomic nanocluster  $\text{Co}_3(\text{py})_3\text{Co}_6\text{Se}_8\text{L}_6$  (py = pyridine, L =  $\text{Ph}_2\text{PN}(\text{ToI})$ ), and ditopic linkers. Post-synthetically, the 3D crystals can be mechanically exfoliated into ultrathin flakes (8 to 60 nm), or intercalated with the redox-active guest tetracyanoethylene in a single-crystal-to-single-crystal transformation. Extensive characterization, including by single crystal X-ray diffraction, reveals how intrinsic features of the nanocluster, such as its structure, chirality, redox-activity and magnetic profile, predetermine key properties of the emerging 2D structures. Within the nanosheets, the strict and unusual stereoselectivity of the nanocluster's Co edges for the low symmetry ( $\alpha,\alpha,\beta$ ) isomer gives rise to in-plane structural anisotropy, while the helically chiral nanoclusters self-organize into alternating  $\Delta$ - and  $\Lambda$ -homochiral rows. The nanocluster's high-spin Co edges, and its rich redox profile make the nanosheets both magnetically and electrochemically active, as revealed by solid state magnetic and cyclic voltammetry studies. The length and flexibility of the ditopic linker was varied, and found to have a secondary effect on the structure and stacking of the nanosheets within the 3D crystals. With these results we introduce a deterministic and versatile synthetic entry to programmable functionality and symmetry in 2D superatomic crystals.

Received 24th June 2020  
Accepted 1st August 2020

DOI: 10.1039/d0sc03506h

rsc.li/chemical-science

## Introduction

The dimensionality of a material is a key determinant of its properties, as demonstrated especially over the past two decades with the isolation of two-dimensional (2D) atomic crystals.<sup>1</sup> These materials have opened new frontiers in exotic physics,<sup>2</sup> catalysis<sup>3</sup> and nanotechnology,<sup>4</sup> yet they face several limitations including relatively low chemical addressability,

and difficulty to access high quality flakes at scale. An attractive route to circumvent these challenges is to prepare “programmable” 2D hierarchical crystals using superatomic building blocks of predetermined structural and physicochemical properties.<sup>5–12</sup> Examples of solid state 2D hierarchical materials exist, for example the semiconductor  $\text{Re}_6\text{Se}_8\text{Cl}_2$ , formed of layers of interlinked Chevrel-like cluster units,<sup>13,14</sup> yet only a handful of reports of cluster-assembled 2D superatomic crystals have been synthesized thus far *via* a bottom-up approach.<sup>12,15–19</sup>

Although wide libraries of atomically precise inorganic clusters of different sizes, compositions and properties are available,<sup>20,21</sup> there are critical synthetic challenges to using them as superatomic building blocks. For example, access to 2D cluster-assembled materials is inhibited by the intrinsic high symmetry of the cluster cores. Typically prepared under thermodynamic control in one-pot syntheses, inorganic clusters have many chemically indistinguishable surface sites. Upon assembly, these degenerate surface sites bind indiscriminately to linkers and give rise to three dimensional structures.<sup>22–26</sup> Synthetic strategies to deliberately lower the symmetry of the

<sup>a</sup>Department of Chemistry, University of Washington, Seattle, Washington 98195, USA. E-mail: avelian@uw.edu

<sup>b</sup>Department of Physics, University of Washington, Seattle, Washington 98195, USA

<sup>c</sup>Department of Chemistry and Chemical Biology, Harvard University, Cambridge, Massachusetts 02138, USA

<sup>d</sup>Department of Materials Science and Engineering, University of Washington, Seattle, Washington 98195, USA

† Electronic supplementary information (ESI) available: Experimental procedures and characterization data including CIF files for 1, 2-bpy, 2-bpy $\sigma$ , 2-bpy $\pi$ , and [2-bpy $\sigma$ ][TCNE]<sub>2</sub>. CCDC 2012111, 2012112, 2012110, 2012109 and 2012108. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0sc03506h



nanocluster blocks could address this challenge.<sup>25,27</sup> For example, site-differentiation, achieved empirically under stoichiometric control, has enabled the synthesis of the low symmetry linear *trans*-Co<sub>6</sub>Se<sub>8</sub>(PEt<sub>3</sub>)<sub>4</sub>(CNC<sub>6</sub>H<sub>4</sub>NC)<sub>2</sub> cluster, which in turn seeded the growth of 1D chains.<sup>16,28</sup> More commonly though dimensional control is obtained serendipitously.<sup>18,19</sup> For example, equipping the degenerate capping ligands with functional groups designed to interlink clusters *via* coordinative,  $\pi$ - $\pi$  or H-bonding, has produced 2D cluster frameworks.<sup>9,15,17</sup>

These strategies, however, are either not deterministic or they lack versatility, and rely heavily on using the organic capping ligands as linkers, limiting further the potential to tailor the structural and electronic properties of cluster-assembled materials. For example, in-plane anisotropy, found in many inorganic solid state van der Waals materials, is a highly desirable structural feature as it provides distinct in-plane pathways for electronic and thermal transport.<sup>29</sup> Still, deterministically encoding it in atomically precise materials remains a synthetic challenge. Most commonly, in reticular materials, in-plane anisotropy occurs serendipitously as the inorganic nodes self-assemble *in situ*, but it can be deliberate when using asymmetric, or mixtures of organic linkers.<sup>18,30-32</sup> Directing in-plane anisotropy by relying on structural features of the inorganic nodes instead is desirable, but requires access to preformed blocks with distinct low symmetries. This strategy has been successfully demonstrated using anisotropic colloidal nanoparticles,<sup>33,34</sup> but not for atomically precise inorganic clusters. This work represents, to the best of our knowledge, the first such example.

Our group developed a generalizable strategy to deliberately lower the symmetry of existing nanoclusters by decorating their inorganic cores with addressable linker-binding sites. Specifically, we recently introduced the synthesis of the helically chiral nanocluster, Fe<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub> (L = Ph<sub>2</sub>PN(Tol), Ph = phenyl, Tol = 4-tolyl), obtained by functionalizing the surface of the Chevrel-type cluster Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub><sup>H</sup> (L<sup>H</sup> = Ph<sub>2</sub>PNHTol) with three Fe edges.<sup>35</sup> Oriented at the vertices of a triangle, the iron sites are poised to function as linker-attachment points that would impose 2D growth upon assembly with linear linkers. A quick evaluation of Fe<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub> as a building block for self-assembly reveals a critical limitation: the Fe edges have very low affinities for external ligands. Here, we find that by simply replacing the Fe with Co, the edge sites become not only competent attachment points for linear ditopic linkers, but also unusual inorganic stereocenters with strict stereoselectivity for a low symmetry isomer. The 2D cluster-assembled materials obtained from these nanoclusters represent exceedingly rare examples where preformed building blocks encode their key structural and physical properties, including in-plane anisotropy, quasi-chiral domains as well as rich redox activity and magnetism. Remarkably, these synthetic 2D superatomic crystals are amenable to post-synthetic manipulations, including exfoliation to ultrathin flakes, and intercalation with guest molecules in a single-crystal-to-single-crystal transformation that highlights their rich, and robust redox profile.

## Results and discussion

### Synthesis and characterization of nanocluster building block 1

We illustrate the versatility of our synthetic strategy to program nanoclusters through the facile synthesis of the tricobalt variant, prepared similarly to Fe<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub>.<sup>35</sup> With increased affinity of the edge sites for external ligands, the tricobalt nanopropeller is isolated exclusively as the tris-pyridine adduct Co<sub>3</sub>(py)<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub> (**1**, 81% yield, Scheme 1). In nanocluster **1**, each Co edge is anchored  $\kappa^3$  to the cluster core *via* two amides, and one surface selenium (Fig. 1). The slow exchange of the surface-bound pyridines in benzene-*d*<sub>6</sub>, and the resultant lower symmetry of the nanocluster are reflected in a very broad <sup>1</sup>H NMR spectrum. Dissolution in pyridine-*d*<sub>5</sub> dramatically speeds up ligand exchange, giving rise to seven, comparatively sharper L proton signals, suggestive of the pseudo-*D*<sub>3</sub> symmetry of **1**.

Nanocluster **1** contains two distinct Co environments: three exposed tetrahedral Co “edge” sites doubling as linker-attachment points, and six square pyramidal Co “core” sites. X-ray diffraction analysis reveals two remarkable structural features, consequential to using **1** as a pre-templated inorganic building block for nanomaterials. One is the intrinsic helicity of **1**, isolated as a ( $\Delta/\Lambda$ ) racemic pair, stemming from the propeller geometry of its inorganic core.<sup>35</sup> The other is the stereogenic nature of the Co edge sites. The stereoisomerism of **1** is easiest understood by analogy to isomerism in 1,2,3-trisubstituted cyclopropanes, where the three substituents are either all oriented on the same face of the ring, or one points to the opposite side from the other two. Similarly, the three edge Co atoms define a triangle that separates two Co<sub>3</sub>Se<sub>4</sub> hemispheres of the Co<sub>6</sub>Se<sub>8</sub> nanocube, with each edge-binding site containing an above-the-plane ( $\alpha$ -Se) and beneath-the-plane ( $\beta$ -Se) selenium atom (Fig. 1). Upon coordination, pyridine formally displaces one of the Se atoms from a  $\kappa^4$ -bound Co edge site, to yield an  $\alpha$ - or a  $\beta$ -bound edge site. Each Co surface site effectively discriminates between the two structurally equivalent  $\alpha$ ,  $\beta$  selenium atoms, and creates three discrete edge Co stereocenters. In turn, these stereocenters orient the bound pyridine above or beneath the plane of the Co edge sites, akin to the isomers of 1,2,3-trisubstituted cyclopropane.

Remarkably, in the solid state, **1** is completely stereoselective for the formation of the low symmetry ( $\alpha,\alpha,\beta$ ) diastereomer. Searching the literature for examples of stereoisomerism in trinuclear clusters, we find they overwhelmingly favor the



Scheme 1 Synthesis of tritopic nanoblock **1**; L<sup>H</sup> = Ph<sub>2</sub>PNH(Tol); py = pyridine.





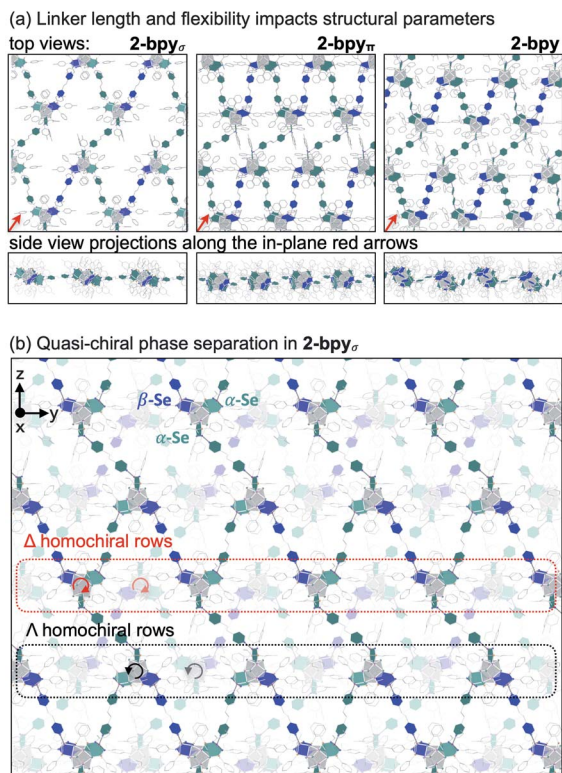


Fig. 2 (a) Single crystal X-ray structure for single layers of **2-bpy**, **2-bpy<sub>σ</sub>** and **2-bpy<sub>π</sub>** (top and side views), illustrating the variations in tile sizes and layer corrugation. (b) In-plane anisotropy and quasi-chiral phase separation in **2-bpy<sub>σ</sub>**. Linkers and nanopropeller blades are colored blue when linked to  $\beta$ -Se, and teal when associated with  $\alpha$ -Se sites.

packed along diagonal lattice planes, and their layers are significantly more separated, by 1.40 and 1.33 nm, respectively.

Within the nanosheets, the racemic mixture of helical nanopropellers undergoes quasi-chiral phase separation within the nanosheets, segregating into alternating  $\Delta$ - and  $\Lambda$ -homochiral rows (Fig. 2b). This phenomenon, wherein a racemic mixture of enantiomers spontaneously separates into enantiomerically pure domains upon assembly, was first observed in monolayers of chiral organic molecules deposited on surfaces,<sup>45,46</sup> and more recently also in 3D frameworks.<sup>47</sup> **2-bpy**, **2-bpy<sub>σ</sub>** and **2-bpy<sub>π</sub>** represent examples where quasi-chiral separation is a guiding force in the self-assembly of 2D frameworks. Notably, the homochiral rows are also aligned vertically in the 3D lattice of **2-bpy<sub>σ</sub>**, opening intriguing possibilities for harnessing emerging optoelectronic properties associated with the individual homochiral domains within the 3D crystals.

### Solid state magnetic analysis

One trait that distinguishes **1** from other reported superatomic building blocks is the high-spin electronic configuration of the Co edge sites. Here, we find that within the nanosheets, the individual magnetic properties of the nanoblock **1** are unaltered. This is illustrated in Fig. 3a, which depicts the virtually identical magnetic responses of nanoblock **1** and nanosheet **2-**

**bpy<sub>π</sub>**. Similar results are observed for the other two derivatives, **2-bpy** and **2-bpy<sub>σ</sub>**, with minor deviations at high temperatures for the latter (Fig. S9†). Given the similarity between the magnetic response of the nanosheets with the monomeric precursor, we focused our interpretation of these properties on those of **1**. Featuring a triangle of high-spin Co(II) sites that inscribes a hexametallate  $\text{Co}_6\text{Se}_8$  core, formally  $(\text{Co}^{\text{III}})_4(\text{Co}^{\text{II}})_2$ , nanopropeller **1** offers a rare opportunity to study the magnetic interaction between paramagnetic ions mediated through a well-defined inorganic support.<sup>48</sup> Within the nanoblock **1**, the magnetic properties are dominated by the three  $S = 3/2$  Co(II) edge sites. Above 150 K, the magnetic susceptibility of **1** is greater than expected for three non-interacting Co(II) ions ( $7.2$  vs.  $5.6 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ ,  $g = 2.0$ ). This discrepancy is expected for the distorted-tetrahedral Co(II) edges, and stems from unquenched orbital angular momentum contributions to the spin-only susceptibility ( $g = 2.28$ ).<sup>49,50</sup> Reduced magnetization data, which resists saturation up to a maximum field of 7 T at 1.8 K, corroborates this interpretation and confirms the presence of a high-spin ground state (Fig. 3b). Below 150 K, the magnetic susceptibility decreases steadily, reaching a minimum of  $2.9 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$  at 2 K. We interpret this behavior to be a combined result of weak antiferromagnetic exchange between the three Co edge sites, also reflected in the negative Weiss constant ( $\theta = -10.5 \text{ K}$ ),<sup>51</sup> and localized anisotropy of the Co(II)



Fig. 3 Post-assembly, **1** preserves its individual magnetic properties within the nanosheets. (a) Plotted are the variable-temperature dc magnetic susceptibility ( $\chi_M T$ , filled circles), the reciprocal molar susceptibility ( $1/\chi_M$ , hollow circles) data for nanoblock **1** (blue) and nanosheet **2-bpy<sub>π</sub>** (teal), collected between 25 to 300 K, at 0.1 T, and the linear fit (25 to 150 K) used to obtain the Weiss constant. (b) Variable-temperature, variable-field reduced magnetization data for **1**, collected upon warming from 1.8 to 10 K at each applied field.



edges. As intra- and intermolecular edge site Co...Co distances are prohibitively long for through-space magnetic exchange ( $>9$  Å),<sup>52</sup> we propose the antiferromagnetic coupling is mediated through the diamagnetic Co<sub>6</sub>Se<sub>8</sub> core.<sup>53</sup> Considering that the previously reported Re<sub>5</sub>OsSe<sub>8</sub> cluster core, diamagnetic and isostructural with Co<sub>6</sub>Se<sub>8</sub>, has been shown to prevent the magnetic interaction between surface bound  $S = 1/2$  Cu(II) ions, antiferromagnetic coupling between the edge  $S = 3/2$  Co in **1** was initially surprising. The different behavior observed in **1** may stem in part from the increased spin response of the Co(II) ions. We propose that the high-spin Co(II) sites interact through low-lying Van Vleck paramagnetic spin states within the Co<sub>6</sub>Se<sub>8</sub> core, which resemble magnetic interactions reported in Co<sub>6</sub>Te<sub>8</sub> and Ni<sub>9</sub>Te<sub>6</sub> clusters.<sup>54</sup> Alternatively, the edge Co may interact with the core *via* intervalence charge transfer processes that may be enabled at low temperature.

### Electrochemical analysis

Nanocluster **1** exhibits a total of five quasi-reversible one-electron redox events spanning 2.5 V and six oxidation states, between  $-2$  and  $+3$  (Fig. 4). Randles–Sevcik analysis confirms that each redox process is chemically reversible within the diffusion-limit.<sup>35,55,56</sup> Interestingly, the robust binding of pyridine to the Co edge sites is reflected in an electrochemical profile completely insensitive to the presence of a coordinating solvent. The first two oxidation events in **1** occur at similar potentials to those observed for Fe<sub>3</sub>-Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub> and the parent cluster Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub><sup>H</sup>, suggesting these remain localized on the Co<sub>6</sub>Se<sub>8</sub> core, and do not involve the edge Co sites. Additionally, in Fe<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub> we determined that the LUMO, estimated electrochemically as the first reduction event, was localized on the Co<sub>6</sub>Se<sub>8</sub> core and stabilized relative to Co<sub>6</sub>-Se<sub>8</sub>L<sub>6</sub><sup>H</sup>. We attributed this stabilization to the Lewis acidity of the edge sites that withdraw electron density from the core through the binding Se. In **1**, donation from the electron rich pyridine ligands effectively decreases the Lewis acidity of the Co edge sites, which in turn leads to a larger HOMO–LUMO gap than that of the

Fe derivative (1.01 vs. 0.79 eV), but still markedly smaller than that of parent cluster (1.44 eV).

To probe the electronic states of the assembled nanosheets, we dropcast crystalline material on a glassy carbon working electrode. Fig. 4 depicts the comparison between the electrochemical profile of the nanocluster **1**, acquired in solution, and that of the **2-bpy**<sub>σ</sub> nanosheets. We discover that the rich redox behavior of the nanopropeller nodes is preserved upon assembly, and the nanosheets exhibit three well-resolved oxidation processes and one irreversible reduction event, all at potentials effectively coinciding with those of nanocluster **1**. The irreversibility of the  $-1/0$  event is not surprising, and we attribute it to the decrease in the Co edge binding affinity for the pyridyl linker, which in turn would be associated with the dissolution of the nanosheet. A similar redox-state controlled affinity for ligands was observed for the triiron nanocluster Fe<sub>3</sub>Co<sub>6</sub>Se<sub>8</sub>L<sub>6</sub>. Finally, we found the linker has a minimal impact on the electrochemical behavior of the cluster nodes. **2-bpy** and **2-bpy**<sub>π</sub> exhibit similar redox profiles to that of **2-bpy**<sub>σ</sub>, though slight variations in the half-wave potentials, peak-to-peak separation and reversibility of peaks are observed, and documented in Table S3† and Fig. S15a.†

### Mechanical exfoliation of **2-bpy**<sub>σ</sub> into ultrathin nanosheets

The individual nanosheets assembled from nanocluster **1** are structurally robust, and can be isolated as ultrathin atomic crystals, behaving akin to solid state inorganic van der Waals 2D materials.<sup>12</sup> Indeed, **2-bpy**<sub>σ</sub> can be successfully exfoliated using the Scotch tape method (Fig. 5c and d).<sup>57</sup> Optical microscopy imaging of the exfoliated crystals reveals their layered structure, along with a well-defined, thickness-dependent color contrast. Atomic force microscopy analysis shows the exfoliated flakes depicted in Fig. 5d have large lateral dimensions (6–15 μm), flat surfaces, and a well-defined lamellar structure with steps ranging between 10 and 30 nm. The thickness of these flakes ranges from 60 nm to as low as 8 nm (*ca.* 8 layers). Examples of bottom-up assembled 2D materials that could be exfoliated or prepared as few or mono-layers primarily include organic<sup>58,59</sup> or hybrid<sup>60–62</sup> reticular frameworks. However, 2D cluster-assembled materials—attractive for their promise of function programmability—that have been successfully exfoliated are exceedingly scarce. In addition to **2-bpy**<sub>σ</sub>, there are only two other examples, a 2D framework interconnected through the capping ligands by zinc-carboxylate nodes, and a hybrid nanosheet in which individual clusters are sandwiched between sheets of photopolymerized C<sub>60</sub>.<sup>15,17</sup>

### Redox intercalation

Redox intercalation into layered materials is a powerful strategy to post-synthetically alter structural, electronic, or magnetic properties.<sup>63</sup> For example, ion intercalation has been used to switch between insulating and semiconductor behaviors in a 2D metal–organic framework,<sup>64</sup> or to tune the conductive properties of the cluster-assembled donor–acceptor solid.<sup>65</sup> Testing our ability to predictably introduce dopants *via* nondestructive post-synthetic techniques, we investigated the intercalation of



Fig. 4 Solution and solid state cyclic voltammograms of **1** and **2-bpy**<sub>σ</sub>, respectively, recorded in DCM (solid lines), THF (dotted lines) or MeCN (dashed lines) solutions of TBAPF<sub>6</sub> (0.1 M), at a scan rate of 200 mV s<sup>-1</sup>. The data for **2-bpy**<sub>σ</sub> was recorded by dropcasting crystalline material on a glass carbon disk electrode.





assembled materials for use as atomically defined anodes in battery materials.<sup>68</sup> The ease of mechanical exfoliation to ultrathin superatomic crystals, and single-crystal-to-single-crystal intercalation with TCNE demonstrates the emerging nanosheets are structurally and chemically robust, providing a potent strategy to encrypt desired functionality in superatomic 2D materials.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors thank Dr T. A. Betley (Harvard University), Dr J.-H. Chu, and P. Malinowski (UW Physics) for assistance with magnetic measurements, and D. Rogers (UW Chemistry) for assistance with X-ray diffraction measurements. This research was supported by a National Science Foundation (NSF) through a Faculty Early Career Development Program award (NSF CAREER 1944843), and through a Seed Grant from the Materials Research Science and Engineering Center at UW (DMR 1719797 AM005). J. A. K. was supported in part through a UW Clean Energy Institute fellowship. C. G. R. is grateful for support from the Clean Energy Bridge to Research REU (NSF 1559787).

## References

- 1 K. S. Novoselov, D. Jiang, F. Schedin, T. J. Booth, V. V. Khotkevich, S. V. Morozov and A. K. Geim, *Proc. Natl. Acad. Sci.*, 2005, **102**, 10451–10453.
- 2 M. Yankowitz, S. Chen, H. Polshyn, Y. Zhang, K. Watanabe, T. Taniguchi, D. Graf, A. F. Young and C. R. Dean, *Science*, 2019, **363**, 1059–1064.
- 3 D. Deng, K. S. Novoselov, Q. Fu, N. Zheng, Z. Tian and X. Bao, *Nat. Nanotechnol.*, 2016, **11**, 218–230.
- 4 G. Fiori, F. Bonaccorso, G. Iannaccone, T. Palacios, D. Neumaier, A. Seabaugh, S. K. Banerjee and L. Colombo, *Nat. Nanotechnol.*, 2014, **9**, 768–779.
- 5 P. Alivisatos, P. F. Barbara, A. W. Castleman, J. Chang, D. A. Dixon, M. L. Klein, G. L. McLendon, J. S. Miller, M. A. Ratner, P. J. Rossky, S. I. Stupp and M. E. Thompson, *Adv. Mater.*, 1998, **10**, 1297–1336.
- 6 E. A. Doud, A. Voevodin, T. J. Hochuli, A. M. Champsaur, C. Nuckolls and X. Roy, *Nat. Rev. Mater.*, 2020, **5**, 371–387.
- 7 Z. Ji, C. Trickett, X. Pei and O. M. Yaghi, *J. Am. Chem. Soc.*, 2018, **140**, 13618–13622.
- 8 N. E. Horwitz, J. Xie, A. S. Filatov, R. J. Papoular, W. E. Shepard, D. Z. Zee, M. P. Grahn, C. Gilder and J. S. Anderson, *J. Am. Chem. Soc.*, 2019, **141**, 3940–3951.
- 9 S. A. Baudron, P. Batail, C. Coulon, R. Clérac, E. Canadell, V. Laukhin, R. Melzi, P. Wzietek, D. Jérôme, P. Auban-Senzier and S. Ravy, *J. Am. Chem. Soc.*, 2005, **127**, 11785–11797.
- 10 B. D. Yuhas, A. L. Smeigh, A. P. S. Samuel, Y. Shim, S. Bag, A. P. Douvalis, M. R. Wasielewski and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2011, **133**, 7252–7255.
- 11 M. J. Turo, L. Chen, C. E. Moore and A. M. Schimpf, *J. Am. Chem. Soc.*, 2019, **141**, 4553–4557.
- 12 L. G. Beauvais, M. P. Shores and J. R. Long, *Chem. Mater.*, 1998, **10**, 3783–3786.
- 13 B. Choi, K. Lee, A. Voevodin, J. Wang, M. L. Steigerwald, P. Batail, X. Zhu and X. Roy, *J. Am. Chem. Soc.*, 2018, **140**, 9369–9373.
- 14 E. J. Telford, J. C. Russell, J. R. Swann, B. Fowler, X. Wang, K. Lee, A. Zangiabadi, K. Watanabe, T. Taniguchi, C. Nuckolls, P. Batail, X. Zhu, J. A. Malen, C. R. Dean and X. Roy, *Nano Lett.*, 2020, **20**, 1718–1724.
- 15 A. M. Champsaur, J. Yu, X. Roy, D. W. Paley, M. L. Steigerwald, C. Nuckolls and C. M. Bejger, *ACS Cent. Sci.*, 2017, **3**, 1050–1055.
- 16 A. M. Champsaur, C. Mézière, M. Allain, D. W. Paley, M. L. Steigerwald, C. Nuckolls and P. Batail, *J. Am. Chem. Soc.*, 2017, **139**, 11718–11721.
- 17 K. Lee, B. Choi, I. J.-L. Plante, M. V. Paley, X. Zhong, A. C. Crowther, J. S. Owen, X. Zhu and X. Roy, *Angew. Chem., Int. Ed.*, 2018, **57**, 6125–6129.
- 18 M. J. Alhilaly, R.-W. Huang, R. Naphade, B. Alamer, M. N. Hedhili, A.-H. Emwas, P. Maity, J. Yin, A. Shkurenko, O. F. Mohammed, M. Eddaoudi and O. M. Bakr, *J. Am. Chem. Soc.*, 2019, **141**, 9585–9592.
- 19 R.-W. Huang, X.-Y. Dong, B.-J. Yan, X.-S. Du, D.-H. Wei, S.-Q. Zang and T. C. W. Mak, *Angew. Chem., Int. Ed.*, 2018, **57**, 8560–8566.
- 20 S. A. Claridge, A. W. Castleman, S. N. Khanna, C. B. Murray, A. Sen and P. S. Weiss, *ACS Nano*, 2009, **3**, 244–255.
- 21 A. W. Cook and T. W. Hayton, *Acc. Chem. Res.*, 2018, **51**, 2456–2464.
- 22 T. Wu, R. Khazhaky, L. Wang, X. Bu, S.-T. Zheng, V. Chau and P. Feng, *Angew. Chem., Int. Ed.*, 2011, **50**, 2536–2539.
- 23 M. P. Shores, L. G. Beauvais and J. R. Long, *J. Am. Chem. Soc.*, 1999, **121**, 775–779.
- 24 S. Jin and F. J. DiSalvo, *Chem. Mater.*, 2002, **14**, 3448–3457.
- 25 Z.-Y. Wang, M.-Q. Wang, Y.-L. Li, P. Luo, T.-T. Jia, R.-W. Huang, S.-Q. Zang and T. C. W. Mak, *J. Am. Chem. Soc.*, 2018, **140**, 1069–1076.
- 26 R.-W. Huang, Y.-S. Wei, X.-Y. Dong, X.-H. Wu, C.-X. Du, S.-Q. Zang and T. C. W. Mak, *Nat. Chem.*, 2017, **9**, 689–697.
- 27 N. Zheng, X. Bu, H. Lu, L. Chen and P. Feng, *J. Am. Chem. Soc.*, 2005, **127**, 14990–14991.
- 28 A. M. Champsaur, A. Velian, D. W. Paley, B. Choi, X. Roy, M. L. Steigerwald and C. Nuckolls, *Nano Lett.*, 2016, **16**, 5273–5277.
- 29 C. Wang, G. Zhang, S. Huang, Y. Xie and H. Yan, *Adv. Opt. Mater.*, 2020, **8**, 1900996.
- 30 N. Huang, L. Zhai, D. E. Coupry, M. A. Addicoat, K. Okushita, K. Nishimura, T. Heine and D. Jiang, *Nat. Commun.*, 2016, **7**, 12325.
- 31 G. S. Papaefstathiou, T. Friščić and L. R. MacGillivray, *J. Am. Chem. Soc.*, 2005, **127**, 14160–14161.
- 32 X.-H. Bu, W. Weng, J.-R. Li, W. Chen and R.-H. Zhang, *Inorg. Chem.*, 2002, **41**, 413–415.
- 33 S. C. Glotzer and M. J. Solomon, *Nat. Mater.*, 2007, **6**, 557–562.



- 34 Y. Liu, K. Deng, J. Yang, X. Wu, X. Fan, M. Tang and Z. Quan, *Chem. Sci.*, 2020, **11**, 4065–4073.
- 35 J. A. Kephart, B. S. Mitchell, A. Chirila, K. J. Anderton, D. Rogers, W. Kaminsky and A. Velian, *J. Am. Chem. Soc.*, 2019, **141**, 19605–19610.
- 36 F. A. Cotton, R. Llusar and C. T. Eagle, *J. Am. Chem. Soc.*, 1989, **111**, 4332–4338.
- 37 M. P. Robben, P. H. Rieger and W. E. Geiger, *J. Am. Chem. Soc.*, 1999, **121**, 367–375.
- 38 B. K. Park, C. Y. Lee, J. Jung, J. H. Lim, Y.-K. Han, C. S. Hong and J. T. Park, *Angew. Chem., Int. Ed.*, 2007, **46**, 1436–1439.
- 39 M. C. Comstock, T. Prussak-Wieckowska, S. R. Wilson and J. R. Shapley, *Organometallics*, 1997, **16**, 4033–4040.
- 40 X. Fan, J. Wang, K. Wu, L. Zhang and J. Zhang, *Angew. Chem., Int. Ed.*, 2019, **58**, 1320–1323.
- 41 C. B. Williamson, D. R. Nevers, A. Nelson, I. Hadar, U. Banin, T. Hanrath and R. D. Robinson, *Science*, 2019, **363**, 731–735.
- 42 Y. Chen, C. Liu, Q. Tang, C. Zeng, T. Higaki, A. Das, D.-E. Jiang, N. L. Rosi and R. Jin, *J. Am. Chem. Soc.*, 2016, **138**, 1482–1485.
- 43 N. Nilius, E. D. L. Rienks, H.-P. Rust and H.-J. Freund, *Phys. Rev. Lett.*, 2005, **95**, 066101.
- 44 W. Xu and J. B. Adams, *Surf. Sci.*, 1995, **339**, 241–246.
- 45 Y. Cai and S. L. Bernasek, *J. Am. Chem. Soc.*, 2003, **125**, 1655–1659.
- 46 T. Huang, Z. Hu, A. Zhao, H. Wang, B. Wang, J. Yang and J. G. Hou, *J. Am. Chem. Soc.*, 2007, **129**, 3857–3862.
- 47 F. Zhang, T. Yajima, Y.-Z. Li, G.-Z. Xu, H.-L. Chen, Q.-T. Liu and O. Yamauchi, *Angew. Chem., Int. Ed.*, 2005, **44**, 3402–3407.
- 48 E. G. Tulsky, N. R. M. Crawford, S. A. Baudron, P. Batail and J. R. Long, *J. Am. Chem. Soc.*, 2003, **125**, 15543–15553.
- 49 J. R. Pilbrow, *J. Magn. Reson.*, 1978, **31**, 479–490.
- 50 S. Sottini, G. Poneti, S. Ciattini, N. Levesanos, E. Ferentinos, J. Krzystek, L. Sorace and P. Kyritsis, *Inorg. Chem.*, 2016, **55**, 9537–9548.
- 51 R. L. Carlin, *Magnetochemistry*, Springer Berlin Heidelberg, Berlin, Heidelberg, 1986.
- 52 T. Mochizuki, T. Nogami and T. Ishida, *Inorg. Chem.*, 2009, **48**, 2254–2259.
- 53 D. Fenske, J. Ohmer and J. Hachgenei, *Angew. Chem., Int. Ed.*, 1985, **24**, 993–995.
- 54 T. T. M. Palstra, M. L. Steigerwald, A. P. Ramirez, Y.-U. Kwon, S. M. Stuczynski, L. F. Schneemeyer, J. V. Waszczak and J. Zaanen, *Phys. Rev. Lett.*, 1993, **71**, 1768–1771.
- 55 A. J. Bard and L. R. Faulkner, *Electrochemical methods: fundamentals and applications*, Wiley, New York, 2nd edn, 2001.
- 56 R. H. Sánchez, A. M. Willis, S.-L. Zheng and T. A. Betley, *Angew. Chem., Int. Ed.*, 2015, **54**, 12009–12013.
- 57 C. Tan, X. Cao, X.-J. Wu, Q. He, J. Yang, X. Zhang, J. Chen, W. Zhao, S. Han, G.-H. Nam, M. Sindoro and H. Zhang, *Chem. Rev.*, 2017, **117**, 6225–6331.
- 58 J. W. Colson, A. R. Woll, A. Mukherjee, M. P. Levendorf, E. L. Spitler, V. B. Shields, M. G. Spencer, J. Park and W. R. Dichtel, *Science*, 2011, **332**, 228–231.
- 59 P. Kissel, D. J. Murray, W. J. Wulfange, V. J. Catalano and B. T. King, *Nat. Chem.*, 2014, **6**, 774–778.
- 60 M. Zhao, Y. Huang, Y. Peng, Z. Huang, Q. Ma and H. Zhang, *Chem. Soc. Rev.*, 2018, **47**, 6267–6295.
- 61 R. Zhang, J. Liu, Y. Gao, M. Hua, B. Xia, P. Knecht, A. C. Papageorgiou, J. Reichert, J. V. Barth, H. Xu, L. Huang and N. Lin, *Angew. Chem., Int. Ed.*, 2020, **59**, 2669–2673.
- 62 Y. Quan, G. Lan, Y. Fan, W. Shi, E. You and W. Lin, *J. Am. Chem. Soc.*, 2020, **142**, 1746–1751.
- 63 J. Wan, S. D. Lacey, J. Dai, W. Bao, M. S. Fuhrer and L. Hu, *Chem. Soc. Rev.*, 2016, **45**, 6742–6765.
- 64 N. Ogihara, N. Ohba and Y. Kishida, *Sci. Adv.*, 2017, **3**, e1603103.
- 65 E. S. O'Brien, M. T. Trinh, R. L. Kann, J. Chen, G. A. Elbaz, A. Masurkar, T. L. Atallah, M. V. Paley, N. Patel, D. W. Paley, I. Kymissis, A. C. Crowther, A. J. Millis, D. R. Reichman, X.-Y. Zhu and X. Roy, *Nat. Chem.*, 2017, **9**, 1170–1174.
- 66 J. S. Miller, *Angew. Chem., Int. Ed.*, 2006, **45**, 2508–2525.
- 67 B. Choi, J. Yu, D. W. Paley, M. T. Trinh, M. V. Paley, J. M. Karch, A. C. Crowther, C.-H. Lee, R. A. Lalancette, X. Zhu, P. Kim, M. L. Steigerwald, C. Nuckolls and X. Roy, *Nano Lett.*, 2016, **16**, 1445–1449.
- 68 A. P. Aydt, B. Qie, A. Pinkard, L. Yang, Q. Cheng, S. J. L. Billinge, Y. Yang and X. Roy, *ACS Appl. Mater. Interfaces*, 2019, **11**, 11292–11297.

