

Cite this: *Mater. Adv.*, 2021,  
2, 7336

# Progress and perspective on chiral plasmonic nanostructures enabled by DNA programming methodology

Hao Yang, Huacheng Li, Pan Tang and Xiang Lan \*

Chirality, a fascinating property ubiquitous in nature, plays an important role in living organisms. DNA-programmed self-assembly has been extensively applied to precisely organize metal nanoparticles and/or small molecules in a chiral fashion at the nanometer scale. These assemblies exhibit significant chiroptical activities and are potential in biological detection and imaging, information processing, optical metamaterials, etc. In this review, we conclude on the DNA-enabled chiral plasmonic systems, uniquely from the perspective of the evolution of DNA programming methodology. We start by introducing a variety of natural and artificial DNA nanostructures to illustrate the fine programmability of DNA. Then we discuss the broad library of DNA-programmed chiral plasmonic nanostructures, spanning from individual nanoparticle–molecule chiral hybrids to the hierarchical chiral arrangements of nanoparticles enabled by DNA nanostructures of different complexities, which are from the primary DNA double helix to advanced architectures. Some cutting-edge applications of DNA-programmed chiral plasmonic nanostructures will also be introduced. We conclude this review with our personal perspectives on the future challenges and opportunities in this rapidly developing field. We expect this comprehensive review will inspire future studies in chiral materials at the convergence of DNA nanotechnology and chiral plasmonics.

Received 31st August 2021,  
Accepted 2nd October 2021

DOI: 10.1039/d1ma00781e

rsc.li/materials-advances

## 1. Introduction

The word “chirality” comes from Greek  $\chi\epsilon\iota\rho$  and it means “hand”. As the name suggests, one of our hands cannot superimpose onto the other (its mirror image) through translations or rotations. In general, chirality refers to the structure attribute of an object without a mirror plane or inversion symmetry. Since Pasteur<sup>1</sup> first separated two types of mirror-image crystals of the sodium ammonium salt of “paratartaric acid”, chirality has long been a central subject in chemistry, because of the extreme importance of chiral configurations/conformations and chirality recognition of many small molecules and biomolecules in playing their functions.

The chirality of a molecule is manifested when interacting with the spin of photons of left- (LH) and right-handed (RH) circularly polarized light. Such differential interactions will lead to optical rotatory dispersion effect (ORD) and unequal optical absorption, *i.e.*, circular dichroism (CD), which are associated with the real and imaginary part of the refractive

index of the chiral molecular media, respectively. However, the chiral strength of a molecule is rather weak. According to the well-established coupled-dipole theory, it is dependent on the couplings between co-linear components of electric and magnetic dipole transitions of the molecule, which are usually very tiny.<sup>2</sup>

In contrast to small molecules, when an incident light of a specific wavelength interacts with metal nanoparticles (NPs), localized surface plasmon resonances (LSPR), that is the collective oscillation of free electrons, can be excited.<sup>3,4</sup> Closely-spaced metal NPs generate strong plasmonic couplings and lead to a significantly enhanced local electromagnetic field in the narrow gap, called “hotspot”.<sup>5–7</sup> Such plasmonic couplings give rise to a wealth of novel collective optical phenomena such as Fano resonances,<sup>8</sup> surface-enhanced Raman scattering (SERS),<sup>9</sup> optical magnetism,<sup>10</sup> and giant chirality.<sup>11</sup> Moreover, the LSPR properties of metal NPs are highly dependent on particle size, shape, composition and the surrounding environment,<sup>12,13</sup> which enable a broad parameter space to modulate the emerging photonic and optoelectronic properties.

Of particular interest is the plasmonic chirality of metal nanostructures, which has so far exhibited a huge potential in various scenarios, such as ultrasensitive enantiomeric sensing,<sup>14</sup>

Xiang Lan Research Group, State Key Laboratory for Modification of Chemical Fibers and Polymer Materials, Center for Advanced Low-dimension Materials, Donghua University, No. 2999 North Renmin Str, Songjiang Dist, Shanghai, 201620, P. R. China. E-mail: xlan@dhu.edu.cn



biomedicine,<sup>15,16</sup> super-resolution imaging,<sup>17</sup> photocatalysis,<sup>18</sup> metamaterials,<sup>19,20</sup> to name a few. Plasmonic chirality mainly originates from three different mechanisms: (a) nanocrystals with obvious chiral morphology, including chiral lattice distortion, twisted metal surface, or whole asymmetric shape.<sup>21–23</sup> Due to their intrinsic chiral morphology and resulting asymmetric LSPR modes, these nanocrystals exhibit strong chiroptical effects; (b) the Coulomb interaction between adsorbed chiral molecules and metal NPs.<sup>7,24–27</sup> It has been reported that Coulombic dipole coupling of a chiral molecule to an achiral plasmonic NP can enhance the molecular chiral signal and induce a new observed chiral plasmonic peak in the visible range. Because of the high polarizability of inorganic nanomaterials, such a chiral mechanism exists in many hybrid systems incorporating chiral ligands; (c) chiral arrangements of achiral NPs.<sup>28</sup> When metal NPs are arranged into a chiral geometry, their plasmons can couple, mix and hybridize with each other, which causes resonance energy splitting under LH and RH circularly polarized light, thus exhibiting characteristic chiral responses.

Undoubtedly, in order to finely manipulate the light responses of chiral plasmonic nanostructures and enhance their optical dissymmetry, known as *g*-factor, reliable nanofabrication with precise control over multiple geometric parameters, such as spatial positions, orientations and even hierarchical arrangements of NPs are stringently required and have been continuously developed in recent decades. Noticeably, the field of chiral plasmonics has so far witnessed a blossom of DNA nanotechnology as a powerful nanofabrication method. Arising from the programmability, nanoscale addressability, robust designability of DNA and the ease of DNA functionalization of nanomaterials, DNA nanotechnology has evolved to be one of the state-of-the-art nanofabrication methods in the creation of unprecedented chiral plasmonic nanostructures, whose chiroptical responses can be rationally tailored and customized *via* DNA molecular programming.<sup>29–31</sup>

In this review, we will highlight the DNA-enabled chiral plasmonic systems, uniquely from the perspective of the evolution of DNA programming methodology. First, a brief background of DNA nanotechnology will be introduced, in order to illustrate the fine programmability of DNA molecular structures. Subsequently, a library of DNA-programmed chiral plasmonic nanostructures will be shown in order from the individual NP–molecule chiral hybrids to the hierarchical chiral arrangements of NPs. DNA origami-enabled chiral organizations of NPs will be emphasized here, as they are increasingly manifested in this field. Then, we will present some examples of the current applications of DNA-programmed chiral plasmonic nanostructures. Lastly, we will conclude this review with our personal view on the future challenges and directions of this highly cross-disciplinary research field. Note that the chiral NPs with intrinsically asymmetric morphologies are beyond the scope of this review. Also, for more theoretical understanding of the plasmonic chirality based on analytical models, we refer readers to the relevant research papers and reviews.<sup>32–35</sup>

## 2. A brief background of DNA nanotechnology

### 2.1 Natural recipes of DNA

Since Watson and Crick<sup>36</sup> first revealed the mystery of DNA structure demonstrating the principle of complementary base-pairing in 1953, the molecular biology age had been officially opened. Deoxynucleotides are structural units of DNA and have four different DNA bases: A (adenine), C (cytosine), G (guanine) and T (thymine). The neighboring deoxynucleotides are linked by phosphodiester bonds to form the phosphate backbone. A single DNA strand of a specific sequence of bases can hybridize with the antiparallel complementary strand through hydrogen bonding, forming the Watson–Crick base-pairing (A–T, C–G). The hybridized strands twist into a double-helical structure for maximum hydrophobic stacking interactions.

Apart from the canonical B-form DNA RH helix found by Watson and Crick, there are two other primary conformations of DNA helices: A-DNA, which is also RH but more rigid than B-DNA;<sup>37,38</sup> and Z-DNA, which is surprisingly LH and found in some eukaryotic genomes.<sup>39</sup> In addition to three helical structures, researchers have found various other DNA conformations that enriched the structural diversity of DNA, such as triplex (H-DNA),<sup>40</sup> mini dumbbells,<sup>41</sup> intermediate Holliday junction.<sup>42</sup> Some nucleic acid aptamers with G-rich sequences are folded into four-stranded structures with the help of metal ions (Fig. 1A).<sup>43–45</sup> The *i*-motif structure is composed of several stretches of C-rich sequences to form a quadruplex structure with C:C+ base pairs at acidic pH (Fig. 1B).<sup>46–48</sup> TTTA or CCTG repeats were found to fold into mini dumbbells (Fig. 1C).<sup>41</sup> To carry more genetic information, DNA molecules are compacted to constitute superstructures such as DNA supercoils.


There are numerous reports on the properties of DNA molecules and it is believed that the structural features and parameters greatly influence their biological functions, for example, gene regulation, DNA replication and repair, although some are considered to be the incentives of genetic disorders. On the other hand, the sequence-defined structural diversity and excellent physicochemical properties make DNA an ideal programmable material for the design of artificial molecular structures that will be introduced in the next section.

### 2.2 Artificial DNA nanostructures

In 1982, Seeman<sup>49</sup> designed an immobile four-arm Holliday junction, which originally took DNA as construction materials and laid the foundation of the theoretical framework for the emerging research field: Structural DNA Nanotechnology. This symmetrical DNA structure, also called “DNA tile”, was expected to create periodic superlattices through hybridizations between the sequence-specific sticky ends. Inspired by this concept, a variety of DNA nanostructures with great geometric and topological complexity were fabricated.

Afterwards, Fu *et al.*<sup>50</sup> introduced the crossover structures between DNA double helices and created several double-crossover tiles (DX tiles) for realizing stable DNA linkages. Mao *et al.*<sup>51</sup> fused four Holliday junctions together to construct



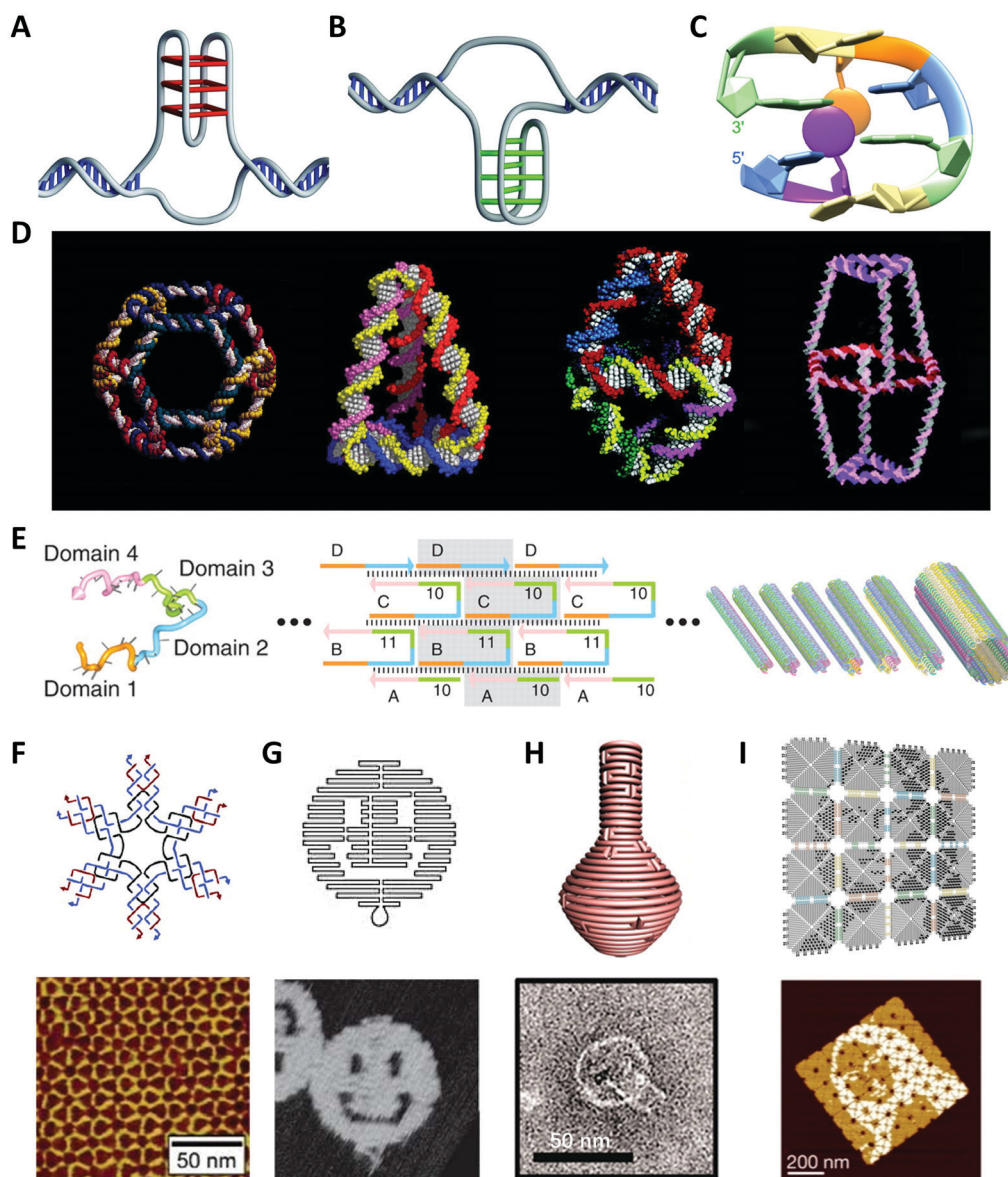

**Fig. 1** The native or artificial DNA structures. (A) Four-stranded G-quadruplex structure.<sup>48</sup> Reproduced from ref. 48 with permission from the Nature Publishing Group. (B) I-motif structure.<sup>48</sup> Reproduced from ref. 48 with permission from the Nature Publishing Group. (C) Native mini dumbbell structure.<sup>41</sup> Reproduced from ref. 41 with permission from the American Chemical Society. (D) The synthesized 3D discrete DNA structures. From left to right: truncated octahedron,<sup>56</sup> tetrahedron,<sup>57</sup> bipyramid,<sup>63</sup> biprism.<sup>64</sup> Reproduced from ref. 56 with permission from the American Chemical Society. Reproduced from ref. 57 with permission from the AAAS. Reproduced from ref. 63 with permission from the American Chemical Society. Reproduced from ref. 64 with permission from the American Chemical Society. (E) The nanotechnology of SST.<sup>62</sup> Reproduced from ref. 62 with permission from the AAAS. (F) The six-point-star DNA tile and the AFM image of 2D array.<sup>65</sup> Reproduced from ref. 65 with permission from the American Chemical Society. (G), (H) and (I) are well-designed patterns or objects using DNA origami.<sup>66–68</sup> Reproduced from ref. 66 with permission from the Nature Publishing Group. Reproduced from ref. 67 with permission from the AAAS. Reproduced from ref. 68 with permission from the Nature Publishing Group.

rhombus DNA units, which could further self-assemble into two-dimensional (2D) DNA arrays with diamond holes. LaBean *et al.*<sup>52</sup> designed a kind of triple-crossover tile (TX tile) that contains three helices formed by four strands, which was an evolution of DX tile and used for logical computation.<sup>53</sup> Yan *et al.*<sup>54</sup> reported  $4 \times 4$  cross-shaped tiles that could periodically arrange proteins or template highly conductive metallic nanowires.

Watson–Crick base-pairing rules were also applied to the self-assembly of three-dimensional (3D) structures, as illustrated

in Fig. 1D. Seeman *et al.*<sup>55,56</sup> constructed covalently closed cube-like and truncated octahedral DNA nanostructures. Goodman *et al.*<sup>57,58</sup> successfully assembled a series of DNA tetrahedral structures with different sizes by using four single-stranded DNA (ssDNA), which are potential to transport or release drug molecules *in vivo*. Mao *et al.*<sup>59,60</sup> assembled DNA dodecahedral, icosahedral, and buckyball nanocages, which were composed of DNA tiles of different shapes. Shih *et al.*<sup>61</sup> synthesized a reproducible DNA octahedron by folding a





1.7-kilobase ssDNA. Yin *et al.*<sup>62</sup> took some identical 42-base DNA single-stranded tiles (SSTs) with four concatenated modular domains to construct DNA lattices (Fig. 1E). The basic consideration of using SST is to use as few tiles as possible to form the desired 2D structures. Subsequently, Ke *et al.*<sup>69</sup> proposed the concept of “DNA brick” on the basis of SST, which enabled modular self-assembly of well-defined 3D structures from short strands. Numerous regular and irregular assembled structures with DNA tiles were developed, including various periodic arrays (Fig. 1F). However, the accompanying issues have been long exercised by researchers, such as “thermodynamic trap” problem, wide dimension distributions, and high cost.

In 2006, Rothemund<sup>66</sup> invented a revolutionary DNA self-assembly technology to construct arbitrary 2D patterns: DNA origami (Fig. 1G). In short, a single-stranded DNA (ssDNA) scaffold, typically several thousand nucleotides long, is folded into the desired shape by hundreds of short oligonucleotide strands (staples), typically 15–60 nt long, in a manner analogous to knitting. To accurately populate the scaffold path, the scaffold commonly used is derived from the phage M13mp18 that contains 7249 bases. On the one hand, the ssDNA scaffold has neither abundant repeating sequence fragments nor large secondary stem-loop structures. On the other hand, each staple strand possesses a unique sequence to locate in the deterministic position. In contrast to DNA tiles, DNA origami is more stable and supports more complicated designs.<sup>70</sup> Moreover, it allows researchers to ignore the pureness and relative stoichiometric ratio of DNA strands, which dramatically reduces experimental errors and time.

During the last decade, researchers have continuously improved the DNA design approach and have fabricated various DNA origami structures from simple 2D geometry of single-layer to complicated 3D structures (Fig. 1H). However, most of them are sub-100 nm dimensions limited by the length of the scaffold strand and the sequence library. In recent years, researchers have introduced the concept of hierarchical assembly of DNA origami by using similar origami blocks to build arbitrary array geometries *via* shape complementarity or sticky-end association, such as micrometer-scale Mona Lisa pattern (Fig. 1I),<sup>68</sup> gigadalton-scale tube<sup>71</sup> and unfoldable nano books.<sup>72</sup> This multi-stage assembly produces enormous gigadalton-scale ordered structures with even over micrometer sizes, and thus brings possibilities to bridge molecular and macroscopic scales. Overall, the technology of scaffolded DNA origami shows great potentials in multi-scale material design and fabrication.

Recently, dynamic DNA nanotechnology that allows to engineer the reconfigurable DNA structures has renewed interest in this field. The most widespread dynamic regulation approach is the DNA toehold-mediated strand displacement reaction (SDR).<sup>73</sup> The concept of toeholds was introduced by Yurke *et al.*<sup>74</sup> and refers to the single-stranded (sticky) end suspended at the terminus of a DNA duplex, which generally consists of several (6–10) bases. In the process, the added “fuel strand” DNAs hybridize with the toehold region and displace the prehybridized strands through DNA branch migration. Nowadays, the

ability to dynamically manipulate DNA structures has led to many applications, for example, in DNA actuators,<sup>75,76</sup> responsive DNA hydrogels,<sup>77</sup> DNA-controlled drug release,<sup>78</sup> and DNA-computing devices *in vitro*<sup>79</sup> and *in vivo*,<sup>80</sup> *etc.* Therefore, dynamic DNA nanotechnology offers a new dimension for material fabrications toward multiple and complex functionalities.

### 2.3 DNA-nanoparticle conjugates

The power of DNA-programmed fabrication of nanostructures also relies on DNA's ability to encode nanoparticle surfaces *via* DNA sequence design and versatile DNA-nanoparticle conjugation chemistry. The first well-characterized frame was made with gold cores and DNA shells proposed by Mirkin *et al.*<sup>81</sup> Specifically, the citrate capped spherical AuNPs were incubated with alkythiol-modified oligonucleotides in a salt solution to form stable Au-S bonds (Fig. 2). It is necessary to highlight that the DNA monolayer also influences the yield of the following self-assembly. However, this seemingly simple conjugate is actually hard to synthesize in experiments. It is primarily because DNA and AuNPs are both negatively charged and the electrostatic repulsion is pervasive in the mixture, whether between DNA and AuNPs or between DNA strands.<sup>82</sup> The initial method is the stepwise addition of NaCl salt for screening the charge repulsions and promoting DNA adsorptions.<sup>83</sup> Despite strenuous efforts that have been made to improve such “salt-aging” method, the process is still troublesome and time-consuming and may result in irreversible aggregation of AuNPs by carelessness.

To overcome such constraints, Zhang *et al.*<sup>84</sup> achieved fast and quantitative DNA adsorptions on AuNPs using a low pH buffer, providing a new protocol to control the DNA-loading process. Later, they further demonstrated nonthiolated DNA–AuNP conjugates with high loading capacity using the pH-assisted strategy.<sup>85</sup> An alternative method is to insert an oligoethylene glycol (OEG) spacer between a DNA sequence and a terminal thiol group.<sup>86</sup> The OEG spacer favored the adsorption kinetics and shielded electrostatic repulsion between DNA and AuNPs. This method is short-time, free of surfactant, and more importantly, enables the direct immobilization of thiolated molecular beacons (MBs) at physiological pH, offering a new parameter to manipulate the modification of AuNPs. Liu *et al.*<sup>87</sup> suggested that low temperature ( $\sim -20$  °C) was also beneficial to the adsorption process of DNA strands, and could reduce the preparation time to a few minutes. More importantly, the post-thawing conjugates

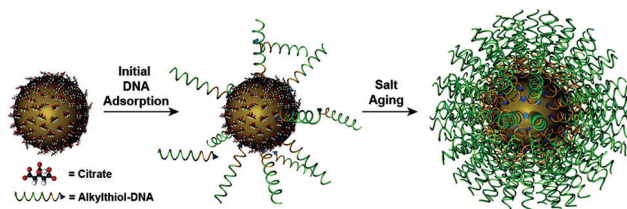


Fig. 2 Schematic of synthesizing the spherical AuNP–thiolated DNA conjugate.<sup>82</sup> Reproduced from ref. 82 with permission from the American Chemical Society.




exhibited higher DNA density than typical salt-aging method (more than 20–30%). Recently, Deng *et al.*<sup>88</sup> synthesized a conjugate with record-high DNA density in seconds by the so-called instant dehydration in butanol (INDEBT) method, in which the principle was butanol extraction.

There is evidence that DNA sequence will affect the overgrowth of NPs due to differential binding affinity between nucleobases and the NP surface, in particular,  $G > A > C > T$ .<sup>89</sup> Wang *et al.*<sup>90–92</sup> discovered that different DNA sequences would induce the growth of NPs into various shapes. For example, NPs would grow to six-point stars in the presence of DNA sequences of T30, while hexagonal nanoplates were formed with G20. Such a DNA-encoded scheme can also direct the overgrowth of anisotropic NPs<sup>93</sup> and even bimetallic NPs.<sup>94</sup> In addition to influencing the NP morphology, the affinity of DNA sequences to NP surface also provides an approach to decorate NPs with tunable multivalency. Yao *et al.*<sup>95,96</sup> utilized this strategy to synthesize many atom-equivalents by programming valence bonds of AuNPs and further constructed colloidal molecules and oligomers.

### 3. Chiral hybrids of nanoparticle and molecules

The DNA molecule is an undoubted natural chiral material. As we mentioned, when chiral biomolecules adsorb on the surfaces of NPs, the hybrid system could exhibit chiroptical responses by Coulombic dipole–dipole interactions, even though they are off-resonance. Govorov *et al.*<sup>97</sup> for the first time theoretically interpreted this inductive effect. In their theoretical framework, an oscillating dipole of the adsorbed chiral molecule induces dissipative chiral currents in the metal NP, which transfers the optical chirality from the molecular absorption band to the plasmon resonances in the visible region (Fig. 3A). Based on such a theory, Li *et al.*<sup>98</sup> explained the origin of the plasmonic chirality of their assemblies, a kind of dsDNA-linked macroscopic gold nanorod (AuNR) aggregate with reversible CD responses through the thermal transition of DNA duplex. They considered the plasmonic chirality coming from the chiral currents induced by DNA rather than the indistinctive chiral arrangement of AuNRs.

Bagheri *et al.*<sup>99</sup> investigated the conjugate of AuNR with folded G-quadruplex and found the intensity increase of CD signal in the visible region. Lu *et al.*<sup>100</sup> obtained a hybrid dandelion-like structure in which ssDNAs were attached on the surface of Au@Ag core/shell nanocubes and radially arranged owing to the electrostatic repulsion (Fig. 3B). The complexes showed two orders of magnitude CD enhancement in the near-visible region, as compared to the DNA native CD signal. Lan *et al.*<sup>101</sup> reported a new hybrid structure with organic chromophores directly self-assembled on the surface of AuNPs in a chiral arrangement through dsDNA hybridization mechanism (Fig. 3C). This strategy of DNA-templated molecular self-assembly allows to accurately control the hierarchical organizations of the chromophores and even their nanoscale

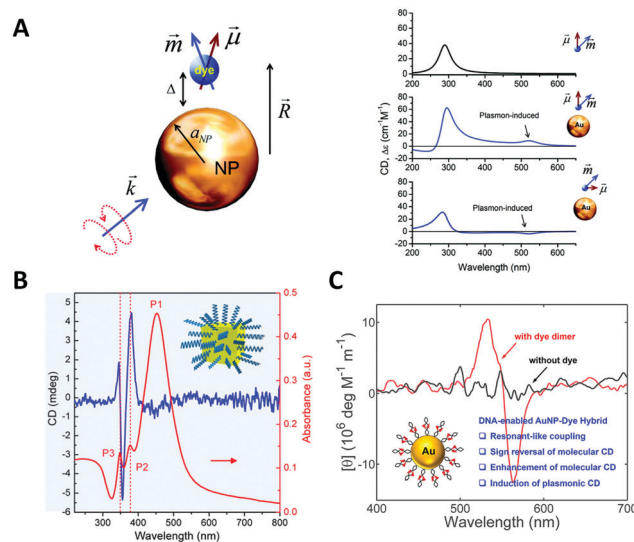


**Fig. 3** Chiral hybrids of molecules and plasmonic NPs. (A) The theoretical model to illustrate the interactions between a metal nanoparticle and a dye molecule (left) and the calculated spectra (right).<sup>97</sup> Reproduced from ref. 97 with permission from the American Chemical Society. (B) The CD and absorbance spectra of dandelion-like DNA–NP hybrids.<sup>100</sup> Reproduced from ref. 100 with permission from the American Chemical Society. (C) The CD spectra of AuNP–dye dimer hybrids templated by dsDNA.<sup>101</sup> Reproduced from ref. 101 with permission from the American Chemical Society.

distances to the NP surface. Although the chromophores used (cyanine dyes) were achiral, they still observed a significant molecular CD signal originating from the templating effect of DNA duplex. Moreover, they found the critical role of resonant plasmon–exciton couplings in reshaping the chiral responses of the hybrids. All these results showed new approaches to fabricate chiral plasmonic nanostructures as individual NPs with chiral adsorbates, illustrating many possibilities not only in the massive production for potential applications, but also in the study of fundamental chiral light–matter interactions, for example, the recently-emerged chiral strong coupling phenomena.<sup>102</sup> Notably, the contribution of induced plasmonic CD to the overall optical activity is much less than the structural chirality in the chiral arrangements of NPs, so it is often neglected in those reports involving structural chirality, intentionally or accidentally.<sup>32</sup>

### 4. Chiral arrangements of nanoparticles based on primary DNA duplex

In 1996, Alivisatos *et al.*<sup>103</sup> reported a landmark work in which they controllably assembled AuNPs into dimers or trimers with defined DNA duplex templates. This work demonstrated the feasibility and potential of using DNA molecules to organize inorganic NPs into discrete nanostructures. The dimer linked by DNA is the simplest self-assembled plasmonic nanostructure. It is a basic and convenient model to understand the complex



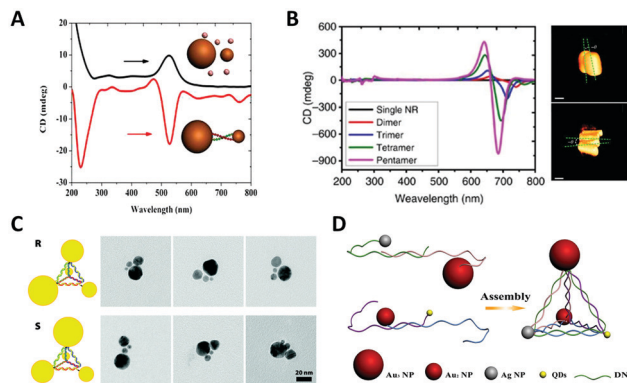

**Fig. 4** Chiral arrangements of NPs induced by primary DNA duplex. (A) The CD spectra of AuNP dimers induced by NaCl (black) and DNA (red), respectively.<sup>105</sup> Reproduced from ref. 105 with permission from the The American Chemical Society. (B) The CD spectra (left) of twisted AuNR assemblies by PCR and the cryo-EM tomography images (right).<sup>107</sup> Reproduced from ref. 107 with permission from the Nature Publishing Group. (C) The AuNP–DNA pyramids.<sup>108</sup> Reproduced from ref. 108 with permission from the American Chemical Society. (D) The heterogeneous pyramid containing AgNP, AuNPs and quantum dots (QDs).<sup>109</sup> Reproduced from ref. 109 with permission from the American Chemical Society.

plasmon couplings that emerged in hierarchical chiral arrangements of NPs.

Note that while AuNP is generally considered to be a perfect sphere, its true shape, according to transmission electron microscopy (TEM) and 3D electron tomography, could be an ellipsoid with a small aspect ratio. In fact, Auguie *et al.*<sup>104</sup> theoretically studied a twisted dimer of ellipsoidal AuNPs separated in the scale of the wavelength of the light, and interpreted the remarkable CD responses from this system as a result of the far-field scattering couplings. Experimentally, Yan *et al.*<sup>105</sup> assembled twisted heterodimers with different-sized AuNPs, which were induced by sodium chloride (NaCl) or DNA (Fig. 4A). They all exhibited high optical activity, resulting from the spontaneous formation of small dihedral angles between adjacent ellipsoidal AuNPs due to electrostatic repulsion and steric hindrance. Here, near-field plasmonic couplings between closely-spaced AuNPs are responsible for their observed CD responses. Hao *et al.*<sup>106</sup> fabricated DNA-directed Au NP-NR asymmetric heterodimers with different CD responses at visible wavelengths by adjusting the gaps between adjacent NPs and altering the size of components; Ma *et al.*<sup>107</sup> tried to assemble AuNR dimers side by side and observed a negative dihedral angle ( $-7.0$  to  $-9.0$  degree) through the TEM tomography (Fig. 4B). Then, they expanded the number of AuNRs by PCR, interestingly, this angle persisted between adjacent nanorods over a long distance, leading to a whole twisted structure with high chiroptical activity.


In general, a tetravalent carbon atom with four different substituents represents an original chiral geometry in stereochemistry. Analogously, Mastroianni *et al.*<sup>108</sup> constructed a NP pyramid by DNA self-assembly. It was assembled with the help of four well-designed ssDNA, where each ssDNA anchored on an AuNP was partially complementary to the others. To break

the symmetry, four AuNPs of different sizes were positioned on the vertices of the pyramid after DNA hybridizations forming a chiral structure (Fig. 4C). Unfortunately, they did not observe any CD signal for some reason. Chen *et al.*<sup>110</sup> reported pyramidal structure mixed with other assemblies in the same year. Notably, there was no selective synthesis or separation of the enantiomers, but it is astonishing that the assemblies showed the preference of a particular chirality for unknown reasons. This is the first experimental observation of chiroptical responses stemming from the coupled plasmon resonances of NP assemblies. Later, they further assembled a heterogeneous pyramid, which contained AgNP, AuNPs and quantum dots (QDs) (Fig. 4D).<sup>109</sup> This hybrid system exhibited obvious and multi-peak chiroptical signals owing to the high yield (80%) and multi-components with distinct optical absorption bands.

## 5. Chiral arrangements of nanoparticles based on scaffold-free DNA tiles

Interestingly, many naturally occurring biomolecules, such as DNA double helix and  $\alpha$ -helix peptide, exhibit an ubiquitous chiral form, a helix. If metal NPs are helically arranged, the coupled collective plasmons show a “corkscrew”-like chiral fashion, a twist of specific handedness resembling the twisted propagation of electric field of LH/RH circularly polarized light, thus resulting in differential optical absorptions.<sup>111</sup> Fundamentally, almost all the optically active objects are helical structures just with differences in the degree of curvature, length scale, or dimension.

Sharma *et al.*<sup>112</sup> reported an early example of NP helix, which existed in a mixture of tube-like NP self-assemblies (Fig. 5A). They designed an array system consisting of four types of DX DNA tiles through sticky-end associations. On one side of the

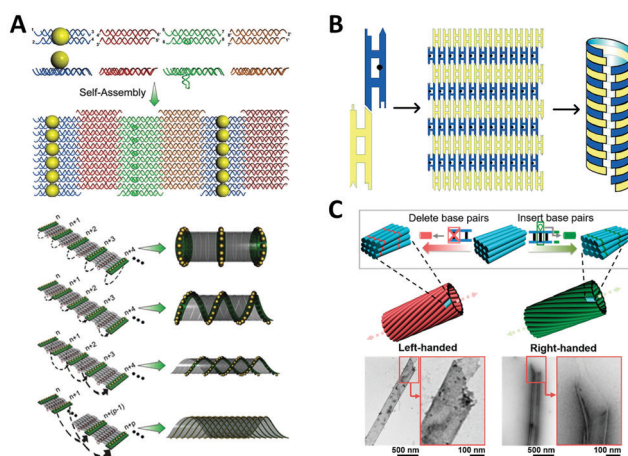

**Fig. 5** Chiral arrangement of metal NPs assisted by scaffold-free DNA tiles. (A) Schematic of the formation of AuNPs helix by four different tiles.<sup>112</sup> Reproduced from ref. 112 with permission from the AAAS. (B) The DNA tube with structural chirality comprising two kinds of tiles.<sup>114</sup> Reproduced from ref. 114 with permission from the American Chemical Society. (C) The large helical tubes designed by SST.<sup>115</sup> Reproduced from ref. 115 with permission from the American Chemical Society.











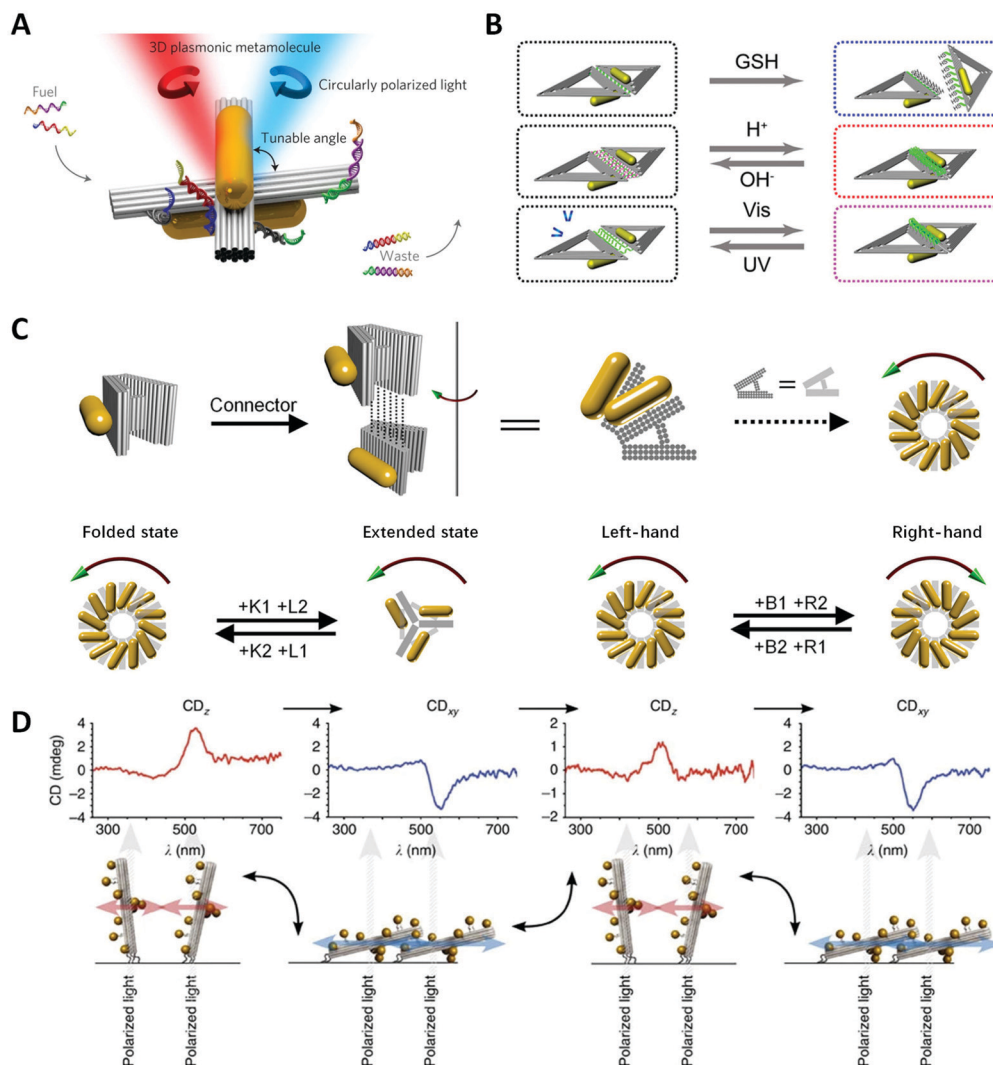


Fig. 7 Dynamic devices based on DNA origami. (A) Reconfigurable twisted AuNR dimer templated by DNA origami.<sup>19</sup> Reproduced from ref. 19 with permission from the Nature Publishing Group. (B) Two AuNRs on rhombus origami can reversibly or irreversibly change the distance under different stimuli.<sup>130</sup> Reproduced from ref. 130 with permission from the American Chemical Society. (C) Reconfigurable chiral helix superstructure of AuNRs.<sup>20</sup> Reproduced from ref. 20 with permission from the American Chemical Society. (D) The manipulation of chiroptical response by relative orientation between the incident light and the AuNP helix.<sup>131</sup> Reproduced from ref. 131 with permission from the Nature Publishing Group.

strategy represents an important success of chiral colloidal self-assembly, enhancing one's ability to dynamically manipulate much more complicated chiral nanostructures, and is also a great step toward the realization of reconfigurable chiroptical devices.

Wang *et al.*<sup>137,138</sup> reported a plasmonic device, where a rotary bundle with extended ssDNAs was connected to a rectangular plate at the bottom *via* a DNA scaffold and was subsequently conjugated with two DNA-functionalized AuNRs. Two pairs of different ssDNAs were placed along the diagonal lines of the origami plate, respectively, which underwent SDR steps to switch the configuration. They stacked up such building units to fabricate a superstructure with four individual chiral centres and finally generated eight stereoisomers. As expected, the arrangement of total-left-hand (LLL) and total-right-hand (RRR) showed the strongest CD signals. For other diastereomers (RRL, RLL, *etc.*), their chiral responses were highly correlated with the

order of chiral centres rather than their simple summation. Aside from altering the structural parameters, Schreiber *et al.*<sup>131</sup> reported a dynamic chiral system by attaching the terminus of an AuNP-helix on the glass surface (Fig. 7D). Upon drying or rehydration, the helix would “lie down” or “stand upright” on the substrate with different orientations to the incident light. The obtained CD spectra of the two states were dynamically reversed because perpendicular and tangential light excitation with respect to the axis of the AuNP helix could lead to distinct plasmonic modes and thus a reversal of the CD lineshape.

## 8. Application

### 8.1 Biodetection

The chiral DNA-nanoparticle assemblies can serve as biocompatible and sensitive probes for bio-detection *in vitro*



and *in vivo*. In contrast to the Förster resonance energy transfer (FRET) method, chiral plasmonic probes are based on polarization optics, diminishing the intensity variation due to fluorescent quenching effect, and thus are stable and highly sensitive. Kuang *et al.*<sup>139</sup> assembled a kind of scissor-like AuNP dimer connected by an anti-bisphenol A (BPA) aptamer and its complementary fragments. In the presence of BPA targets, the dimers disassembled and the chiroptical response was reduced. The amplitude of CD signals would indicate the concentration of BPA in the sample. The limit of detection (LOD) of this aptamer-based method was as low as 0.008 ng mL<sup>-1</sup> in the range of 0.02–5 ng mL<sup>-1</sup>. Li *et al.*<sup>140</sup> constructed DNA-driven gold-upconversion nanoparticle (Au-UCNP) pyramids that could act as intracellular nanoprobe to detect miRNAs in real-time. Based on the structural association and disassociation strategy, it allows detecting the telomerase activity,<sup>141</sup> adenosine-5'-triphosphate (ATP),<sup>142</sup> serum alpha-fetoprotein (AFP),<sup>143</sup> 8-hydroxy-2'-deoxyguanosine (8-OHdG),<sup>144,145</sup> Ag<sup>+</sup> ions<sup>146</sup> and so on. Ma *et al.*<sup>107</sup> obtained chiral twisted side-by-side assemblies of AuNRs through PCR replication procedure and made possible detection of DNA with the LOD as low as 3.7 aM. The introduction of DNA origami technology could offer a reusable platform for the detection of target molecules. Huang *et al.*<sup>147</sup> designed the aptamer-based “locks” into the previously introduced twisted AuNR dimer on DNA origami and switched the lock on/off by inputting the adenosine. Similar AuNR dimers were also applied to detect RNA<sup>128</sup> and thrombin.<sup>148</sup> Zhou *et al.*<sup>149</sup> created a dual-responsive plasmonic system with DNA origami, which was modulated by both aptamer–target interactions and thermal changes, and demonstrated chiroptical detections of ATP and cocaine. Overall, those DNA-programmed chiral plasmonic probes can detect target species with high accuracy and present the subtle specific binding of molecules as significant changes of optical output.

## 8.2 DNA computer

In addition to excellent ability for nanofabrication, the earliest function of DNA is the carrier of genetic information in biology. Nowadays, more and more people consider the use of DNA in information storage and computing, and imagine the transformative DNA computer. DNA computing devices generate, extract and test the logical results of specific problems at the molecular level through natural parallel operations and biochemical processing of a large number of DNA molecules. In fact, Adleman<sup>150</sup> successfully used the coordination of DNA molecules with enzymes to calculate the Hamiltonian path problem as early as 1994. Subsequently, Okamoto *et al.*<sup>151</sup> combined digital circuits with DNA computing and designed DNA logic gates and circuits. The molecular logic gate systems utilized different efficiencies of DNA hole transport through base pairs and generated the output signal when hole transport occurred. Lately, Dong *et al.*<sup>152</sup> introduced the concept of DNA computing into their previous dynamic chiral plasmonic nanostructures. The integrated system could execute a complete set of Boolean logical gates by reading elaborate DNA strands as inputs and returning plasmonic chiroptical signals as outputs. More interestingly, the logic gates could perform different logical functions at different temperatures


even if inputting the same DNA strands, that is to say, they had the adaptability to execute more complicated functions.

## 8.3 Metamaterial and metadvice

Electromagnetic metamaterials are artificially engineered micro(nano)structured materials with attractive electromagnetic properties that are not existing in natural materials. In particular, chiral metamaterials are promising to realize negative refractive index, light polarization control, chirality sensing and so on. The DNA-programmed self-assembly provides a new bottom-up method to manufacture chiral optical metamaterials or meta-devices with superior resolutions. A variety of 3D chiral plasmonic assemblies could act as solution-state metamaterials, also called metafluids. The plasmonic metamolecules obtained by Kuzyk *et al.*<sup>19</sup> realized reconfigurable chirality at the nanoscale, which was difficult for other micro(nano) processing methods. As mentioned above, Lan *et al.*<sup>126</sup> demonstrated chiral metamaterials with distinct helical morphologies by simply connecting different domains of V-shaped DNA origami units addressed with AuNR. This self-assembly strategy also enabled chiral metamaterials with switchable chirality.<sup>20</sup> The successful creation and manipulation of hierarchical chiral nanostructures is essential for studying the fundamental chiral light–matter interactions, and meanwhile, for constructing cross-scale metadvice. In fact, the aforementioned chiral structures, whether static or dynamic, can be regarded as the prototypes of novel optical devices. Such diverse chiral DNA–NP assemblies lay the foundation to fabricate multifunctional optical devices in the future.

## 8.4 Other applications

Recently, Göpfrich *et al.*<sup>153</sup> exploited droplet-based microfluidics to successfully encapsulate DNA-programmed chiral nanostructures inside uniform cell-sized microfluidic compartments. Such a combined system enabled filtration of plasmonic enantiomers efficiently on the microfluidic chip. This strategy inspired researchers to synthesize artificial cells by integrating biochemical molecules such as enzymes in a similar way. Attempts have also been made in the field of energy conversions. Martens *et al.*<sup>154</sup> demonstrated efficient plasmon-assisted long-range chiral interactions through both experiments and simulations. In their model, spherical AuNPs were placed between two separated AuNRs to transfer plasmonic energy. More surprisingly, the simulation illustrated that the transfer effect persisted even for AuNR inter-distance up to 200 nm.<sup>155</sup> This innovative mechanism might bring new insights into the long-distance chiral transfer and the design of new transmitter micro-devices in optical circuits. Previous studies have shown that surface photochemistry and plasmonic nanocrystal growth could be induced by hot electrons (HEs).<sup>156,157</sup> Liu *et al.*<sup>158</sup> introduced the concept of HE generation in the chiral plasmonic nanostructures. In their DNA-templated model system, the HEs were first injected into small TiO<sub>2</sub> nanocrystals from chiral plasmonic AuNR dimers and later transferred to the reactive species. They observed a significant CD in the generation rates of HEs and considered that the chiral optical asymmetry of plasmonic nanostructure was transferred into the HE generations.



Such a mechanism of the chiral photochemical effect is different from conventional chiral photochemistry and has potential for practical applications, such as polarization-sensitive photochemistry.

## 9. Summary and perspective

We have provided a comprehensive overview of the development of chiral nanostructures enabled by DNA, from the aspect of the evolution of DNA programming methodology. Because of the excellent programmability and specific recognition ability of DNA molecules, researchers utilize DNA to program the organizations of NPs in nanoscale precision and create various chiral plasmonic nanostructures, including NP–molecule chiral hybrids, and structurally-chiral systems spanning simple static NP arrangements to sophisticated dynamic organizations at different hierarchical levels. These chiral nanostructures could bring new opportunities in nanophotonics, biodetection, catalysis, DNA computer, microfluidics, and so on.

To date, top-down fabrication technologies, such as electron beam lithography (EBL),<sup>159,160</sup> focused ion beam (FIB) lithography<sup>161</sup> and direct laser writing,<sup>162</sup> have proven to be successful in fabricating chiral nanostructures over a large area and with excellent reproducibility. However, these methods are time- and cost-consuming and the processing of highly complex 3D structures has always been difficult. In the realm of self-assembly, there are also successful examples of using polymers,<sup>163</sup> peptides,<sup>164</sup> and proteins<sup>165</sup> to mediate the chiral assembly of NPs. However, interactions and compatibility between NPs and these templates/inducers need to be further improved to expand the NP material selections. Also, the lack of precise addressability in terms of positional and orientational control has limited the applicability of these strategies to some extent. Moreover, the designability and tunability of these templates/inducers remain to be enhanced to meet the growing demand for the fabrication of chiral nanomaterials.

In this context, DNA self-assembly methodology is manifesting as it becomes increasingly mature. The next focus would be the discovery and advancement of the properties and functions of chiral nanostructures by means of a combinatorial investigation including theoretical modeling, structural designing, advanced spectroscopic characterizations. The goals would at least include the enhancement of *g*-factors to improve the far-field properties and engineering the near fields to enhance the local superchiral fields. Therefore, DNA-mediated anisotropic interactions among new building blocks, which are varied in sizes, compositions, shapes, *etc.*, should be tightly regulated, allowing precise control over the spatial orientation, quantity and inter-distance of the building blocks. It is also highly intriguing to dynamically control and/or switch the properties and functions of chiral nanostructures, for example, by manipulating the chiral self-assembly process or the resulting chiral nanostructures in space and time, with various physical, chemical and/or mechanical external stimuli. Such capability should lead to the development of chiral materials with multi-responsiveness for various applications. To solve these problems, we envision that new

opportunities will arise from the convergence of DNA programming technologies with the new frontiers across fields, including symmetry-breaking NP surface engineering, hybrid nanocomposites, soft/responsive device fabrications, electromagnetic theories, *etc.*

Although DNA fabrication methods are still suffering from the scale-up self-assembly over micrometers with high efficiency, new solutions or possibilities could be offered using the Damascene technology with the patterned substrates for hosting and arranging the DNA-programmed nanostructures, which can indeed circumvent the size limitations for the device-scale fabrications. Such technological integration should open new avenues toward the on-chip chiral photonic/plasmonic devices for many light control applications, such as polarization filtering/conversion and chiral light sources with positioned quantum emitters. Enantiomeric-molecular sensing, an extremely important target in chemistry and biology, is also promising with the DNA programming methodology. In combination with theoretical discovery of the superchiral local field and DNA-programmed nanofabrication, optimal and precise positioning of target enantiomers in the chiral nanostructures can be expected. The single-molecular addressability of DNA can even help push the chiral sensing resolution to the limit of single-molecule level, for example, *via* chiral strong coupling between plasmon and molecular excitons.

In general, artificial self-assembled chiral nanostructures are still limited to the low-order chirality compared to the complex high-order chiral materials existing in nature. The chiral nanostructures obtained at present are considerably simple in both structure and function. We speculate on a new possible development stage of self-assembly of chiral nanostructures toward the integration of multi-components and multi-functionalities, device-scale applications, and intellectualization. DNA programming methodology has evolved to be a powerful modern nanofabrication technology and will boost this rapidly-developing field of chiral materials, with its own continuous advancement and convergence with other areas simultaneously.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

X. Lan gratefully thanks for the grant support from the National Natural Science Foundation of China (No. 22004015).

## References

- 1 L. Pasteur, *Ann. Chim. Phys. Sér. 3*, 1848, **24**, 442–459.
- 2 W. Ma, L. Xu, A. F. d. Moura, X. Wu, H. Kuang, C. Xu and N. Kotov, *Chem. Rev.*, 2017, **117**, 8041–8093.
- 3 N. Halas, S. Lal, W.-S. Chang, S. Link and P. Nordlander, *Chem. Rev.*, 2011, **111**, 3913–3961.





- 4 E. Ozbay, *Science*, 2006, **311**, 189–193.
- 5 L. Kneer, E.-M. Roller, L. Besteiro, R. Schreiber, A. Govorov and T. Liedl, *ACS Nano*, 2018, **12**, 9110–9115.
- 6 E. Severoni, S. Maniappan, L. Liz-Marzán, J. Kumar, F. J. G. d. Abajo and L. Galantini, *ACS Nano*, 2020, **14**, 16712–16722.
- 7 L. Besteiro, H. B. Zhang, J. Plain, G. Markovich, Z. M. Wang and A. Govorov, *Adv. Opt. Mater.*, 2017, **5**, 1700069.
- 8 F. Shafiei, F. Monticone, K. Q. Le, X. Liu, T. Hartsfield, A. Alù and X. Li, *Nat. Nanotechnol.*, 2013, **8**, 95–99.
- 9 X. Lan, Z. Chen, X. Lu, G. Dai, W. Ni and Q. Wang, *ACS Appl. Mater. Interfaces*, 2013, **5**, 10423–10427.
- 10 A. Alù and N. Engheta, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 085112.
- 11 X. Shen, A. Asenjo-Garcia, Q. Liu, Q. Jiang, F. J. G. d. Abajo, N. Liu and B. Ding, *Nano Lett.*, 2013, **13**, 2128–2133.
- 12 K. Kelly, E. Coronado, L. Zhao and G. Schatz, *J. Phys. Chem. B*, 2003, **107**, 668–677.
- 13 L. Liz-Marzán, *Langmuir*, 2006, **22**, 32–41.
- 14 L. Xu, Z. Xu, W. Ma, L. Liu, L. Wang, H. Kuang and C. Xu, *J. Mater. Chem. B*, 2013, **1**, 4478–4483.
- 15 A. Kumar, S. Kumar, W. Rhim, G.-H. Kim and J. Nam, *J. Am. Chem. Soc.*, 2014, **136**, 16317–16325.
- 16 Y.-L. Luo, Y.-S. Shiao and Y.-F. Huang, *ACS Nano*, 2011, **5**, 7796–7804.
- 17 W. Li and X. Chen, *Nanomedicine*, 2015, **10**, 299–320.
- 18 W. Li, J. Miao, T. Peng, H. Lv, J.-G. Wang, K. Li, Y. Zhu and D. Li, *Nano Lett.*, 2020, **20**, 2507–2513.
- 19 A. Kuzzyk, R. Schreiber, H. B. Zhang, A. Govorov, T. Liedl and N. Liu, *Nat. Mater.*, 2014, **13**, 862–866.
- 20 X. Lan, T. Liu, Z. Wang, A. Govorov, H. Yan and Y. Liu, *J. Am. Chem. Soc.*, 2018, **140**, 11763–11770.
- 21 Z. Fan and A. Govorov, *Nano Lett.*, 2012, **12**, 3283–3289.
- 22 G. González-Rubio, J. Mosquera, V. Kumar, A. Pedrazo-Tardajos, P. Llombart, D. M. Solís, I. Lobato, E. Noya, A. Guerrero-Martínez, J. M. Taboada, F. Obelleiro, L. G. Macdowell, S. Bals and L. Liz-Marzán, *Science*, 2020, **368**, 1472–1477.
- 23 H.-E. Lee, H.-Y. Ahn, J. Mun, Y. Y. Lee, M. Kim, N. H. Cho, K. Chang, W. S. Kim, J. Rho and K. Nam, *Nature*, 2018, **556**, 360–365.
- 24 I. Lieberman, G. Shemer, T. Fried, E. Kosower and G. Markovich, *Angew. Chem.*, 2008, **47**, 4855–4857.
- 25 J. Slocik, A. Govorov and R. Naik, *Nano Lett.*, 2011, **11**, 701–705.
- 26 T. Levi-Belenkova, A. Govorov and G. Markovich, *J. Phys. Chem. C*, 2016, **120**, 12751–12756.
- 27 C. Rao, Z. Wang, N. Li, W. Zhang, X. Xu and B. Ding, *Nanoscale*, 2015, **7**, 9147–9152.
- 28 Z. Fan and A. Govorov, *Nano Lett.*, 2010, **10**, 2580–2587.
- 29 A. Ceconello, L. Besteiro, A. Govorov and I. Willner, *Nat. Rev. Mater.*, 2017, **2**, 17039.
- 30 D. Winogradoff, P.-Y. Li, H. Joshi, L. Quednau, C. Maffeo and A. Aksimentiev, *Adv. Sci.*, 2021, **8**, 2003113.
- 31 A. Ceconello and F. Simmel, *Small*, 2019, **15**, e1805419.
- 32 A. Govorov, *J. Phys. Chem. C*, 2011, **115**, 7914–7923.
- 33 A. Govorov and Z. Fan, *ChemPhysChem*, 2012, **13**, 2551–2560.
- 34 Z. Fan, H. Zhang and A. Govorov, *J. Phys. Chem. C*, 2013, **117**, 14770–14777.
- 35 Z. Fan and A. Govorov, *J. Phys. Chem. C*, 2011, **115**, 13254–13261.
- 36 J. Watson and F. Crick, *Nature*, 1953, **171**, 737–738.
- 37 V. Ivanov, L. Minchenkova, A. Schyolkina and A. Poletayev, *Biopolymers*, 1973, **12**, 89–110.
- 38 A. Leslie, S. Arnott, R. Chandrasekaran and R. Ratliff, *J. Mol. Biol.*, 1980, **143**, 49–72.
- 39 G. Schroth, P. Chou and P. Ho, *J. Biol. Chem.*, 1992, **267**, 11846–11855.
- 40 H. Moser and P. Dervan, *Science*, 1987, **238**, 645–650.
- 41 P. Guo and S. L. Lam, *J. Am. Chem. Soc.*, 2016, **138**, 12534–12540.
- 42 F. Hays, Z. Jones and P. Ho, *Biochemistry*, 2004, **43**, 9813–9822.
- 43 D. Sen and W. Gilbert, *Nature*, 1988, **334**, 364–366.
- 44 G. Parkinson, M. Lee and S. Neidle, *Nature*, 2002, **417**, 876–880.
- 45 M. D. Antonio, A. Ponjavic, A. Radzevjičius, R. T. Ranasinghe, M. Catalano, X. Zhang, J. Shen, L.-M. Needham, S. F. Lee, D. Klenerman and S. Balasubramanian, *Nat. Chem.*, 2020, **12**, 832–837.
- 46 A. Phan, M. Guéron and J. Leroy, *J. Mol. Biol.*, 2000, **299**, 123–144.
- 47 H. Day, P. Pavlou and Z. A. E. Waller, *Bioorg. Med. Chem.*, 2014, **22**, 4407–4418.
- 48 M. Zeraati, D. Langley, P. Schofield, A. Moye, R. Rouet, W. E. Hughes, T. M. Bryan, M. Dinger and D. Christ, *Nat. Chem.*, 2018, **10**, 631–637.
- 49 N. Seeman, *J. Theor. Biol.*, 1982, **99**, 237–247.
- 50 T. Fu and N. Seeman, *Biochemistry*, 1993, **32**, 3211–3220.
- 51 C. Mao, W. Sun and N. Seeman, *J. Am. Chem. Soc.*, 1999, **121**, 5437–5443.
- 52 T. LaBean, H. Yan, J. Kopatsch, F. Liu, E. Winfree, J. Reif and N. Seeman, *J. Am. Chem. Soc.*, 2000, **122**, 1848–1860.
- 53 C. Mao, T. LaBean, J. Reif and N. Seeman, *Nature*, 2000, **407**, 493–496.
- 54 H. Yan, S. H. Park, G. Finkelstein, J. Reif and T. LaBean, *Science*, 2003, **301**, 1882–1884.
- 55 J. Chen and N. Seeman, *Nature*, 1991, **350**, 631–633.
- 56 Y. Zhang and N. Seeman, *J. Am. Chem. Soc.*, 1994, **116**, 1661–1669.
- 57 R. Goodman, I. Schaap, C. Tardin, C. Erben, R. Berry, C. Schmidt and A. Turberfield, *Science*, 2005, **310**, 1661–1665.
- 58 R. Goodman, R. Berry and A. Turberfield, *Chem. Commun.*, 2004, 1372–1373.
- 59 Y. He, T. Ye, M. Su, C. Zhang, A. Ribbe, W. Jiang and C. Mao, *Nature*, 2008, **452**, 198–201.
- 60 C. Zhang, M. Su, Y. He, X. Zhao, P. Fang, A. Ribbe, W. Jiang and C. Mao, *Proc. Natl. Acad. Sci. U. S. A.*, 2008, **105**, 10665–10669.
- 61 W. Shih, J. Quispe and G. Joyce, *Nature*, 2004, **427**, 618–621.



- 62 P. Yin, R. Hariadi, S. Sahu, H. M. Choi, S. H. Park, T. LaBean and J. Reif, *Science*, 2008, **321**, 824–826.
- 63 C. Erben, R. P. Goodman and A. Turberfield, *J. Am. Chem. Soc.*, 2007, **129**, 6992–6993.
- 64 F. A. Aldaye and H. Sleiman, *J. Am. Chem. Soc.*, 2007, **129**, 13376–13377.
- 65 Y. He, Y. Tian, A. Ribbe and C. Mao, *J. Am. Chem. Soc.*, 2006, **128**, 15978–15979.
- 66 P. Rothmund, *Nature*, 2006, **440**, 297–302.
- 67 D. Han, S. Pal, J. Nangreave, Z. Deng, Y. Liu and H. Yan, *Science*, 2011, **332**, 342–346.
- 68 G. Tikhomirov, P. Petersen and L. Qian, *Nature*, 2017, **552**, 67–71.
- 69 Y. Ke, L. Ong, W. Shih and P. Yin, *Science*, 2012, **338**, 1177–1183.
- 70 C. Zhou, X. Duan and N. Liu, *Acc. Chem. Res.*, 2017, **50**, 2906–2914.
- 71 K. F. Wagenbauer, C. Sigl and H. Dietz, *Nature*, 2017, **552**, 78–83.
- 72 T. Gerling, K. F. Wagenbauer, A. Neuner and H. Dietz, *Science*, 2015, **347**, 1446–1452.
- 73 F. Simmel, B. Yurke and H. R. Singh, *Chem. Rev.*, 2019, **119**, 6326–6369.
- 74 B. Yurke, A. Turberfield, A. Mills Jr, F. Simmel and J. Neumann, *Nature*, 2000, **406**, 605–608.
- 75 L. L. Hildebrandt, S. Preus, Z. Zhang, N. V. Voigt, K. Gothelf and V. Birkedal, *J. Am. Chem. Soc.*, 2014, **136**, 8957–8962.
- 76 Z. Yu, M. Centola, J. Valero, M. Matthies, P. Šulc and M. Famulok, *J. Am. Chem. Soc.*, 2021, **143**, 13292–13298.
- 77 F. Topuz and O. Okay, *Macromolecules*, 2008, **41**, 8847–8854.
- 78 T. Zhang, J. Nong, N. Alzahrani, Z. Wang, S. W. Oh, T. Meier, D. Yang, Y. Ke, Y. Zhong and J. Fu, *ACS Appl. Mater. Interfaces*, 2019, **11**, 29512–29521.
- 79 J.-H. Lee, S. H. Lee, C. Baek, H.-S. Chun, J.-h. Ryu, J.-W. Kim, R. Deaton and B.-T. Zhang, *BioSystems*, 2017, **158**, 1–9.
- 80 L. Kari, *Future Gener. Comput. Syst.*, 2001, **17**, 823–834.
- 81 C. Mirkin, R. Letsinger, R. Mucic and J. Storhoff, *Nature*, 1996, **382**, 607–609.
- 82 J. I. Cutler, E. Auyeung and C. A. Mirkin, *J. Am. Chem. Soc.*, 2012, **134**, 1376–1391.
- 83 J. Storhoff, R. Elghanian, R. C. Mucic, C. Mirkin and R. Letsinger, *J. Am. Chem. Soc.*, 1998, **120**, 1959–1964.
- 84 X. Zhang, M. Servos and J. Liu, *J. Am. Chem. Soc.*, 2012, **134**, 7266–7269.
- 85 X. Zhang, B. Liu, N. Dave, M. Servos and J. Liu, *Langmuir*, 2012, **28**, 17053–17060.
- 86 Q. Xu, X. Lou, L. Wang, X. Ding, H. Yu and Y. Xiao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 27298–27304.
- 87 B. Liu and J. Liu, *J. Am. Chem. Soc.*, 2017, **139**, 9471–9474.
- 88 Y. Hao, Y. Li, L. Song and Z. Deng, *J. Am. Chem. Soc.*, 2021, **143**, 3065–3069.
- 89 M. Östblom, B. Liedberg, L. Demers and C. Mirkin, *J. Phys. Chem. B*, 2005, **109**, 15150–15160.
- 90 Z. Wang, J. Zhang, J. Ekman, P. Kenis and Y. Lu, *Nano Lett.*, 2010, **10**, 1886–1891.
- 91 Z. Wang, L. Tang, L. H. Tan, J. Li and Y. Lu, *Angew. Chem., Int. Ed.*, 2012, **51**, 9078–9082.
- 92 L. H. Tan, H. Xing and Y. Lu, *Acc. Chem. Res.*, 2014, **47**, 1881–1890.
- 93 T. Song, L. Tang, L. H. Tan, X. Wang, N. S. R. Satyavolu, H. Xing, Z. Wang, J. Li, H. Liang and Y. Lu, *Angew. Chem., Int. Ed.*, 2015, **54**, 8114–8118.
- 94 N. S. R. Satyavolu, L. H. Tan and Y. Lu, *J. Am. Chem. Soc.*, 2016, **138**, 16542–16548.
- 95 G. Yao, H. Pei, J. Li, Y.-z. Zhao, D. Zhu, Y. Zhang, Y. Lin, Q. Huang and C. Fan, *NPG Asia Mater.*, 2015, **7**, e159.
- 96 G. Yao, J. Li, Q. Li, X. Chen, X. Liu, F. Wang, Z. Qu, Z. Ge, R. P. Narayanan, D. Williams, H. Pei, X. Zuo, L. Wang, H. Yan, B. Feringa and C. Fan, *Nat. Mater.*, 2019, **19**, 781–788.
- 97 A. Govorov, Z. Fan, P. Hernandez, J. Slocik and R. Naik, *Nano Lett.*, 2010, **10**, 1374–1382.
- 98 Z. Li, Z. Zhu, W. Liu, Y. Zhou, B. Han, Y. Gao and Z. Tang, *J. Am. Chem. Soc.*, 2012, **134**, 3322–3325.
- 99 Z. Bagheri, B. Ranjbar, A. Azizi, H. Latifi, M. I. Zibaii and T. T. Moghadam, *Sci. Iran.*, 2017, **25**, 1783–1788.
- 100 F. Lu, Y. Tian, M. Liu, D. Su, H. Zhang, A. Govorov and O. Gang, *Nano Lett.*, 2013, **13**, 3145–3151.
- 101 X. Lan, X. Zhou, L. A. McCarthy, A. Govorov, Y. Liu and S. Link, *J. Am. Chem. Soc.*, 2019, **141**, 19336–19341.
- 102 J. Zhu, F. Wu, Z. Han, Y. Shang, F. Liu, H. Yu, L. Yu, N. Li and B. Ding, *Nano Lett.*, 2021, **21**, 3573–3580.
- 103 A. Alivisatos, K. Johnsson, X. Peng, T. Wilson, C. Loweth, M. Bruchez Jr and P. Schultz, *Nature*, 1996, **382**, 609–611.
- 104 B. Auguie, J. Alonso-Gómez, A. Guerrero-Martinez and L. Liz-Marzán, *J. Phys. Chem. Lett.*, 2011, **2**, 846–851.
- 105 W. Yan, W. Ma, H. Kuang, L. Liu, L. Wang, L. Xu and C. Xu, *J. Phys. Chem. C*, 2013, **117**, 17757–17765.
- 106 C. Hao, L. Xu, W. Ma, L. Wang, H. Kuang and C. Xu, *Small*, 2014, **10**, 1805–1812.
- 107 W. Ma, H. Kuang, L. Xu, L. Ding, C. Xu, L. Wang and N. Kotov, *Nat. Commun.*, 2013, **4**, 2689.
- 108 A. J. Mastroianni, S. Claridge and A. Alivisatos, *J. Am. Chem. Soc.*, 2009, **131**, 8455–8459.
- 109 W. Yan, L. Xu, C. Xu, W. Ma, H. Kuang, L. Wang and N. Kotov, *J. Am. Chem. Soc.*, 2012, **134**, 15114–15121.
- 110 W. Chen, A. Bian, A. Agarwal, L. Liu, H. Shen, L. Wang, C. Xu and N. Kotov, *Nano Lett.*, 2009, **9**, 2153–2159.
- 111 H. Liu, X. Shen, Z. Wang, A. Kuzyk and B. Ding, *Nanoscale*, 2014, **6**, 9331–9338.
- 112 J. Sharma, R. Chhabra, A. Cheng, J. Brownell, Y. Liu and H. Yan, *Science*, 2009, **323**, 112–116.
- 113 A. Kuzyk, R. Schreiber, Z. Fan, G. Pardatscher, E.-M. Roller, A. Högele, F. Simmel, A. Govorov and T. Liedl, *Nature*, 2012, **483**, 311–314.
- 114 J. C. Mitchell, J. Harris, J. Malo, J. Bath and A. Turberfield, *J. Am. Chem. Soc.*, 2004, **126**, 16342–16343.
- 115 S. Sun, Y. Yang, D. Li and J. Zhu, *J. Am. Chem. Soc.*, 2019, **141**, 19524–19528.



- 116 X. Shen, C. Song, J. Wang, D. Shi, Z. Wang, N. Liu and B. Ding, *J. Am. Chem. Soc.*, 2012, **134**, 146–149.
- 117 F. Benn, N. E. C. Haley, A. E. Lucas, E. Silvester, S. Helmi, R. Schreiber, J. Bath and A. Turberfield, *Angew. Chem., Int. Ed.*, 2018, **57**, 7687–7690.
- 118 M. J. Urban, P. K. Dutta, P. Wang, X. Duan, X. Shen, B. Ding, Y. Ke and N. Liu, *J. Am. Chem. Soc.*, 2016, **138**, 5495–5498.
- 119 A. Guerrero-Martínez, B. Auguie, J. L. Alonso-Gómez, Z. Džolić, S. Gómez-Graña, M. Žinić, M. Cid and L. Liz-Marzán, *Angew. Chem., Int. Ed.*, 2011, **50**, 5499–5503.
- 120 S. Pal, Z. Deng, H. Wang, S. Zou, Y. Liu and H. Yan, *J. Am. Chem. Soc.*, 2011, **133**, 17606–17609.
- 121 X. Lan, Z. Chen, G. Dai, X. Lu, W. Ni and Q. Wang, *J. Am. Chem. Soc.*, 2013, **135**, 11441–11444.
- 122 X. Shen, P. Zhan, A. Kuzyk, Q. Liu, A. Asenjo-Garcia, H. Zhang, F. D. d. Abajo, A. Govorov, B. Ding and N. Liu, *Nanoscale*, 2014, **6**, 2077–2081.
- 123 Z. Chen, C. K. K. Choi and Q. Wang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 26835–26840.
- 124 X. Lan, X. Lu, C. Shen, Y. Ke, W. Ni and Q. Wang, *J. Am. Chem. Soc.*, 2015, **137**, 457–462.
- 125 X. Lan, Z. Su, Y. Zhou, T. Meyer, Y. Ke, Q. Wang, W. Chiu, N. Liu, S. Zou, H. Yan and Y. Liu, *Angew. Chem., Int. Ed.*, 2017, **56**, 14632–14636.
- 126 P. Wang, J.-H. Huh, H. Park, D. Yang, Y. Zhang, Y. Zhang, J. Lee, S. Lee and Y. Ke, *Nano Lett.*, 2020, **20**, 8926–8932.
- 127 Y. Huang, M.-K. Nguyen and A. Kuzyk, *J. Visualized Exp.*, 2019, **145**, e59280.
- 128 T. Funck, F. Nicoli, A. Kuzyk and T. Liedl, *Angew. Chem., Int. Ed.*, 2018, **57**, 13495–13498.
- 129 A. Kuzyk, M. J. Urban, A. Idili, F. Ricci and N. Liu, *Sci. Adv.*, 2017, **3**, e1602803.
- 130 Q. Jiang, Q. Liu, Y. Shi, Z.-G. Wang, P. Zhan, J. Liu, C. Liu, H. Wang, X. Shi, L. Zhang, J. Sun, B. Ding and M. Liu, *Nano Lett.*, 2017, **17**, 7125–7130.
- 131 R. Schreiber, N. Luong, Z. Fan, A. Kuzyk, P. C. Nickels, T. Zhang, D. M. Smith, B. Yurke, W. Kuang, A. Govorov and T. Liedl, *Nat. Commun.*, 2013, **4**, 2948.
- 132 A. Kuzyk, Y. Yang, X. Duan, S. Stoll, A. Govorov, H. Sugiyama, M. Endo and N. Liu, *Nat. Commun.*, 2016, **7**, 10591.
- 133 J. Ryssy, A. K. Natarajan, J. Wang, A. Lehtonen, M.-K. Nguyen, R. Klajn and A. Kuzyk, *Angew. Chem., Int. Ed.*, 2020, **60**, 5859–5863.
- 134 L. Xin, C. Zhou, X. Duan and N. Liu, *Nat. Commun.*, 2019, **10**, 5394.
- 135 C. Zhou, X. Duan and N. Liu, *Nat. Commun.*, 2015, **6**, 8102.
- 136 M. J. Urban, C. Zhou, X. Duan and N. Liu, *Nano Lett.*, 2015, **15**, 8392–8396.
- 137 M. Wang, J. Dong, C. Zhou, H. Xie, W. Ni, S. Wang, H. Jin and Q. Wang, *ACS Nano*, 2019, **13**, 13702–13708.
- 138 M.-K. Nguyen and A. Kuzyk, *ACS Nano*, 2019, **13**, 13615–13619.
- 139 H. Kuang, H. Yin, L. Liu, L. Xu, W. Ma and C. Xu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 364–369.
- 140 S. Li, L. Xu, W. Ma, X. Wu, M. Sun, H. Kuang, L. Wang, N. Kotov and C. Xu, *J. Am. Chem. Soc.*, 2016, **138**, 306–312.
- 141 M. Sun, L. Xu, F. Pan, W. Xiaoling, H. Kuang, L. Liu and C. Xu, *Adv. Funct. Mater.*, 2016, **26**, 7352–7358.
- 142 P. Fu, M. Sun, L. Xu, X. Wu, L. Liu, H. Kuang, S. Song and C. Xu, *Nanoscale*, 2016, **8**, 15008–15015.
- 143 H. Zhao, S. Bian, Y. Yang and X. Wu, *Microchim. Acta*, 2017, **184**, 1855–1862.
- 144 W. Xiuxiu, L. Xu, C. Hao, C. Xu and H. Kuang, *Environ. Sci. Technol. Lett.*, 2018, **5**, 500–507.
- 145 Y. Liu, M. Wei, L. Zhang, Y. Zhang, W. Wei, L. Yin, Y. Pu and S. Liu, *Anal. Chem.*, 2016, **88**, 6509–6514.
- 146 Z. Xu, L. Xu, L. Liz-Marzán, W. Ma, N. Kotov, L. Wang, H. Kuang and C. Xu, *Adv. Opt. Mater.*, 2013, **1**, 626–630.
- 147 Y. Huang, M.-K. Nguyen, A. K. Natarajan, V. Nguyen and A. Kuzyk, *ACS Appl. Mater. Interfaces*, 2018, **10**, 44221–44225.
- 148 T. Funck, T. Liedl and W. Bae, *Appl. Sci.*, 2019, **9**, 3006.
- 149 C. Zhou, L. Xin, X. Duan, M. J. Urban and N. Liu, *Nano Lett.*, 2018, **18**, 7395–7399.
- 150 L. Adleman, *Science*, 1994, **266**, 1021–1024.
- 151 A. Okamoto, K. Tanaka and I. Saito, *J. Am. Chem. Soc.*, 2004, **126**, 9458–9463.
- 152 J. Dong, M. Wang, Y. Zhou, C. Zhou and Q. Wang, *Angew. Chem., Int. Ed.*, 2020, **59**, 15038–15042.
- 153 K. Göpfrich, M. J. Urban, C. Frey, I. Platzman, J. Spatz and N. Liu, *Nano Lett.*, 2020, **20**, 1571–1577.
- 154 K. Martens, F. Binkowski, L.-D. Nguyen, L. Hu, A. Govorov, S. Burger and T. Liedl, *Nat. Commun.*, 2021, **12**, 2025.
- 155 L. Hu, T. Liedl, K. Martens, Z. Wang and A. Govorov, *ACS Photonics*, 2019, **6**, 749–756.
- 156 E. Cortés, W. Xie, J. Cambiasso, A. S. Jermyn, R. Sundararaman, P. Narang, S. Schlücker and S. Maier, *Nat. Commun.*, 2017, **8**, 14880.
- 157 P. Wang, A. Krasavin, M. Nasir, W. Dickson and A. Zayats, *Nat. Nanotechnol.*, 2017, **13**, 159–164.
- 158 T. Liu, L. Besteiro, T. Liedl, M. Correa-Duarte, Z. Wang and A. Govorov, *Nano Lett.*, 2019, **19**, 1395–1407.
- 159 J. Trevino, H. Cao and L. D. Negro, *Nano Lett.*, 2011, **11**, 2008–2016.
- 160 V. Valev, J. Baumberg, B. D. Clercq, N. Braz, X. Zheng, E. J. Osley, S. Vandendriessche, M. Hojeij, C. Blejean, J. Mertens, C. Biris, V. Volskiy, M. Ameloot, Y. Ekinci, G. Vandenbosch, P. Warburton, V. Moshchalkov, N. Panoiu and T. Verbiest, *Adv. Mater.*, 2014, **26**, 4074–4081.
- 161 A. Drezet, C. Genet, J.-Y. Laluet and T. Ebbesen, *Opt. Express*, 2008, **16**, 12559–12570.
- 162 J. K. Gansel, M. Thiel, M. Rill, M. Decker, K. Bade, V. Saile, G. v. Freymann, S. Linden and M. Wegener, *Science*, 2009, **325**, 1513–1515.
- 163 G. Cheng, D. Xu, Z. Lu and K. Liu, *ACS Nano*, 2019, **13**, 1479–1489.
- 164 J. George and K. G. Thomas, *J. Am. Chem. Soc.*, 2010, **132**, 2502–2503.
- 165 R. Mout, G. Y. Tonga, L.-s. Wang, M. Ray, T. Roy and V. Rotello, *ACS Nano*, 2017, **11**, 3456–3462.

