




Liquid Marble

Review paper from Dr. Tenjimbayashi's Team at National Institute for Materials Science (NIMS), and Prof. Mouterde's Team at the University of Tokyo.

Liquid marbles: review of recent progress in physical properties, formation techniques, and lab-in-a-marble applications in microreactors and biosensors

This review summarises the fundamental properties of liquid marbles, the recent advances (mainly works published in 2020–2023) in the concept of liquid marbles, physical properties, formation methods, liquid marble-templated material design, and biochemical applications. Finally, the potential development and variations of liquid marbles are discussed.

As featured in:



See Mizuki Tenjimbayashi, Timothée Mouterde *et al.*, *Nanoscale*, 2023, 15, 18980.



Cite this: *Nanoscale*, 2023, **15**, 18980

Liquid marbles: review of recent progress in physical properties, formation techniques, and lab-in-a-marble applications in microreactors and biosensors

Mizuki Tenjimbayashi, ^{*a} Timothée Mouterde, ^{*b} Pritam Kumar Roy ^b and Koichiro Uto ^c

Received 3rd October 2023,
Accepted 6th November 2023

DOI: 10.1039/d3nr04966c

rsc.li/nanoscale

Liquid marbles (LMs) are nonsticking droplets whose surfaces are covered with low-wettability particles. Owing to their high mobility, shape reconfigurability, and widely accessible liquid/particle possibilities, the research on LMs has flourished since 2001. Their physical properties, fabrication mechanisms, and functionalisation capabilities indicate their potential for various applications. This review summarises the fundamental properties of LMs, the recent advances (mainly works published in 2020–2023) in the concept of LMs, physical properties, formation methods, LM-templated material design, and biochemical applications. Finally, the potential development and variations of LMs are discussed.

1. Introduction

Transporting small amounts of liquids is essential in various fundamental industrial technologies that experience unwanted liquid adhesion. Nature offered an idea for effective liquid transportation. In 1992, Benton and Foster reported that some gall-forming aphids transport honeydew droplets without sticking by covering them with wax particles.¹ In 2001,

^aResearch Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan.

E-mail: TENJIMBAYASHI.Mizuki@nims.go.jp

^bDepartment of Mechanical Engineering, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan. E-mail: mouterde@g.ecc.u-tokyo.ac.jp

^cResearch Center for Macromolecules and Biomaterials, NIMS, 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan



Mizuki Tenjimbayashi

Mizuki Tenjimbayashi is an independent researcher at the Research Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS). He received his Ph.D. from Keio University in 2017 and joined NIMS in 2018. He specializes in wetting dynamics and surface engineering to design functional materials interfaces with special wettability, such as superhydrophobic surfaces, liquid-infused

surfaces, and liquid marbles. He is highly motivated to use his developments for practical application by joining industry–academia collaboration events.



Timothée Mouterde

Timothée Mouterde graduated from École polytechnique and received his PhD from the Université Paris-Saclay. During his PhD supervised by David Quéré, he worked on antifogging surfaces and the dynamics of Leidenfrost and superhydrophobic drops. He then joined the group of Lydéric Bocquet, (ENS Paris) to study experimentally fluid transport inside angstrom-scale channels. In 2019, he moved to The University of

Tokyo, in Takuro Ideguchi's laboratory, to develop new optical techniques for nanofluidics. In 2021, he started his research group within the Department of Mechanical Engineering of The University of Tokyo. His laboratory focuses on fluid/solid interactions from wetting phenomena to nanofluidics.



Moreover, LMs exhibit shape reconfigurability and can be split or merged repeatedly (Fig. 1C). This shape reconfigurability is unique to LMs, and it is impossible for droplets encapsulated with a bulk film. This indicates that LMs behave as soft solids in the static state. However, they can be split or merged like a fluid by applying a sufficiently strong mechanical force. Thus, LMs resemble a shear-thinning or thixotropic non-Newtonian fluid. Owing to these features and the wide range of possible liquid/particle combinations, LMs have received considerable attention and have been investigated in relation to various interesting domains; accordingly, various LM applications for replacing the inner liquid with fluidic media have been proposed. The wettability of the liquid medium to particles, which is mainly governed by the surface tension, determines the formation of LMs. Examples of liquid media include acidic/alkaline water, cell culture medium, glycerol,


Researchers in the field of colloidal science treat LMs as liquid-in-air emulsions stabilised by particles.²⁰ Beyond the development of LMs, their potential applications have stimulated multidisciplinary research in various fields, including



Pritam Kumar Roy earned his MSc and PhD in Physics from IIT Kanpur. During his PhD, he worked on wetting tunability on soft solid and lubricant-infused surfaces under the supervision of Prof. Krishnacharya Khare. In 2019, he joined Prof. Edward Bormashenko's group at Ariel University, Israel, where he explored magnetic field-induced droplet movement and liquid marbles. He was awarded the Study in Israel Fellowship (PBC



Koichiro Uto is an independent scientist at the Research Center for Macromolecules and Biomaterials at the National Institute for Materials Science (NIMS) where he joined in 2018. He received his Ph.D. degree from Kagoshima University under the guidance of Prof. Takao Aoyagi. His postdoc research was performed with Prof. Cole A. DeForest and Prof. Deok-Ho Kim at the University of Washington. In 2016, he moved



This review covers the recent developments in LMs, mainly works reported after 2020, and highlights cutting-edge scientific findings on the physical properties of LMs, concepts, formation methods, LM-templated material design, and critical applications of lab-in-a-marble. We believe this work will help readers gain a comprehensive understanding of the current and potential development of LMs and related applications. To make this review understandable to general readers, we first review the fundamental properties of LMs in the following section.

When Aussillous and Qu  r   first demonstrated the concept of LMs, they formed a LM by rolling a liquid droplet onto a hydrophobic particle bed. When particles are adsorbed on a liquid interface, the total system energy decreases owing to the minimisation of the surface energy, resulting in the formation of LMs.²⁶ More precisely, with R_p denoting the particle radius and θ the contact angle of the liquid on a particle, for each particle adsorbed on the interface, the system energy decreases by:

$$\Delta G = \pi \gamma R_p^2 (1 - |\cos \theta|) \quad (1)$$

where γ denotes the liquid–air surface tension. This simple calculation shows that both hydrophobic ($\theta > 90^\circ$) and hydrophilic ($\theta < 90^\circ$) particles can be utilised to form LMs;^{9,27} additionally, a stronger decrease in surface energy is observed

2.1 Droplets and LMs

Nonwetting states can be achieved by forming an air layer between the solid and the liquid, for example, by patterning

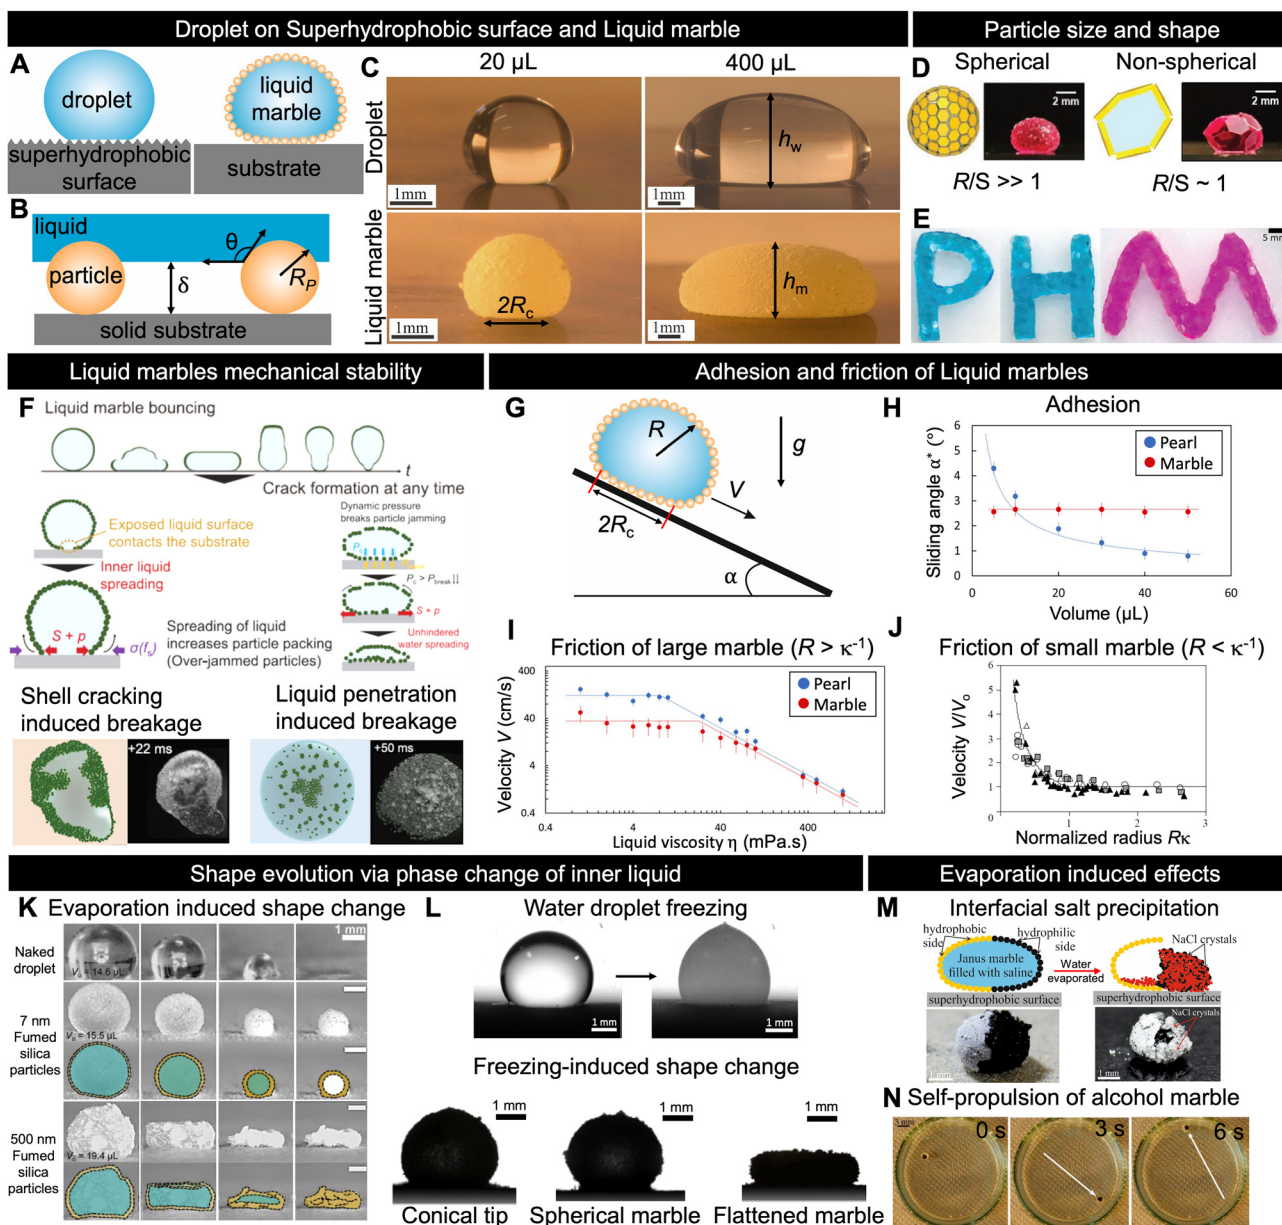


Fig. 2 Fundamental and physical properties. (A) Schematic depicting a pearl (droplets on superhydrophobic surfaces) and LM; in both cases, an air layer is formed between the liquid and substrate. (B) Sketch of air layer formed by particles adsorbed on the LM surface. The air layer thickness, δ , depends on the particle radius R_p and liquid/solid contact angle θ . (C) Images of LMs and pearls made with water and lycopodium with volume 20 and 400 μL , respectively. (D), (E) Various LM shapes achievable with different particle sizes depending on the ratio between LM radius R and particle size S .^{49,94} (F) Different scenarios illustrating how LMs break upon impact.¹⁵ (G), (H), (I) and (J) Effects of adhesion and friction on the motion of LMs and pearls.^{25,26} (K) and (L) Shape evolution of water droplets and LMs during phase change of the inner liquid.^{66,67,71} (M) Depiction of salt crystallisation at the interface⁷⁷ and (N) self-propulsion of Janus marble in water bath during the evaporation of inner liquid from LMs.⁸¹ Copyrights: (D) Reproduced from ref. 49 under CC BY 4.0 Wiley-VCH GmbH 2020; (E) reproduced from ref. 94 with permission from Wiley-VCH GmbH, Copyright 2019; (F) reproduced from ref. 15 with permission from Wiley-VCH GmbH, Copyright 2021; (H) and (I) reproduced from ref. 25 with permission from the American Institute of Physics, Copyright 2023; (J) reproduced from ref. 26 with permission from the Royal Society, Copyright 2006; (K) reproduced from ref. 66 with permission from the Royal Society of Chemistry, Copyright 2021; (L) reproduced from ref. 67 and 71 with permission from the Elsevier Ltd., Copyright 2018 and from the Elsevier, 2021; (M) reproduced from ref. 77 with permission from the American Chemical Society, Copyright 2021; (N) reproduced from ref. 81 with permission from the American Chemical Society, Copyright 2015.

for particle wetting properties between hydrophobic and hydrophilic surfaces. Here, θ can be estimated by microscopic observation of the gel-trapped or polymerized liquid-air interface^{28,29} using SEM, environmental-SEM, or a digital

microscope. Force measurement techniques, such as colloidal probe atomic force microscopy, can also be used to measure θ .³⁰ Consequently, Zang *et al.* reported that LMs covered with particles with θ close to 90° exhibit the highest mechanical

This journal is © The Royal Society of Chemistry 2023

Nanoscale, 2023, 15, 18980-18998 | 18985

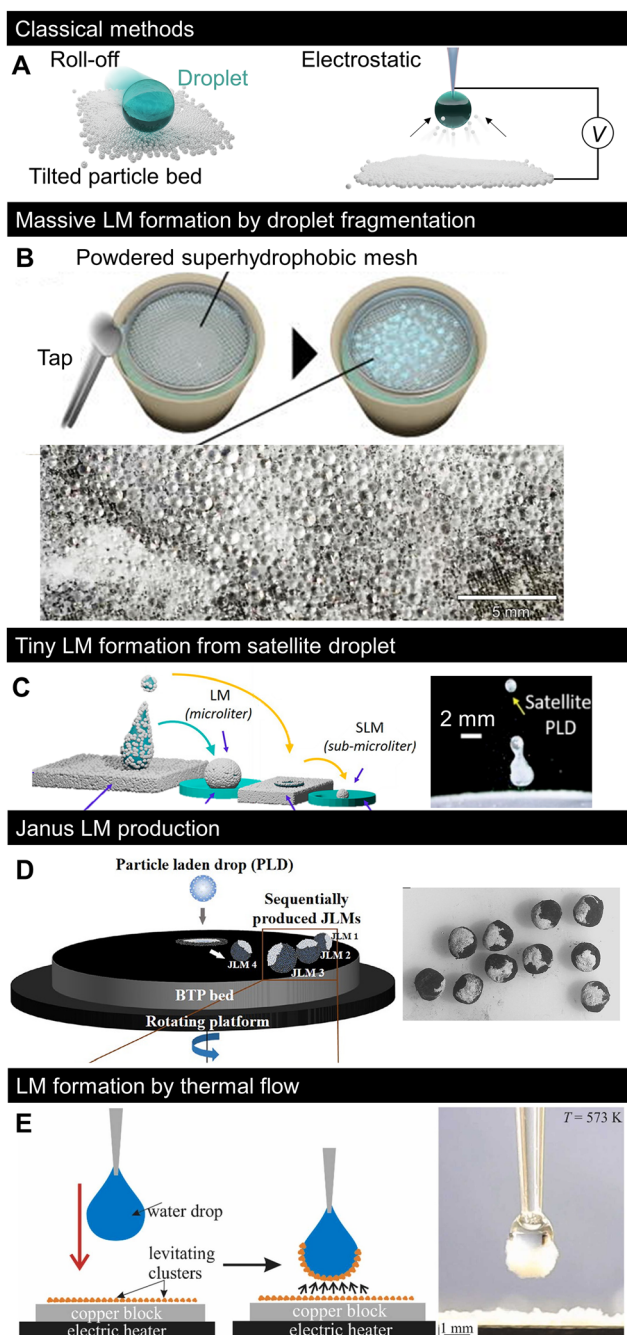


Fig. 3 Recent progress in LM formation methods. (A) Classical LM formation method: roll-off (left) and electrostatic methods (right). (B) Massive formation of tiny LMs by applying impulsive pressure to powdered superhydrophobic mesh on water pool.⁸⁷ (C) Formation of tiny LMs by covering the impacting satellite droplets with particles.⁸⁸ (D) Continuous formation of Janus LMs by impacting a particle-laden droplet onto other types of particle beds.⁸⁹ (E) Covering droplets with thermally levitating nanoparticles.⁹⁰ Copyrights: (B) Reproduced from ref. 87 with permission from the American Institute of Physics, Copyright 2023; (C) reproduced from ref. 88 with permission from the American Chemical Society, Copyright 2022; (D) reproduced from ref. 89 with permission from the American Chemical Society, Copyright 2020; (E) reproduced from ref. 90 with permission from Elsevier, Copyright 2022.

it is difficult to mass-produce LMs using this formation process. Janus LMs can be formed by LM impacts on surfaces covered with different types of particles (Fig. 3D).⁸⁹ When LM impacts the particle bed, it deforms and a part of the inner liquid surface is exposed.⁵⁰ The LM becomes heterogeneous when a second type of particle is attached to the exposed liquid surface. The study in Fig. 3D controlled the impacting behaviour of the fluorine polymer-covered LM on a black toner particle bed to form Janus LMs. The studies introduced in Fig. 3B–D were based on the physical adsorption of particles based on the direct contact of droplets, and several developments in the formation process are expected to form more complex patterns.

3.5 Particle-heating-induced LM formation

While the indirect particle adsorption method was first limited to the previously described electrostatic method (Fig. 3A), the work presented in Fig. 3E proposed another indirect LM formation method⁹⁰ based on thermal flow-induced particle levitation. When a bed of low-density nanoparticles is heated to sufficiently high temperatures (here, 300 °C), the nanoparticles levitate driven by thermal flow and get adsorbed on the droplet surface to form LMs. Overall, simple and convenient LM formation methods have been recently developed.

4. Conceptual variation in LMs

Since the first report on synthetic LMs in 2001,² various studies have attempted to analyse functional LMs based on responsive particles.¹⁶ These studies mostly fit within the category of classical LMs in terms of size, with millimetric and outer granules being powders. Concurrently, attempts to change the shape of granules have been reported. For example, in 2014, Miao *et al.* reported that LMs can be stabilised by silver nanofibers.⁹¹ In 2019, Geyer *et al.* reported a polyhedral LM, wherein a droplet was covered with millimetric polyhedral polymer plates to form a soccer-ball-like morphology.⁴⁹ Owing to the diversity of colloid shapes reported thus far,^{92,93} the LM with non-spherical granules presented a new avenue for designing LMs with unfamiliar shapes, and various subsequent works have been reported.^{76,94} However, conceptual variation is not limited to the particle shape.

4.1 Micro-LMs

Interestingly, since 2020, several studies have proposed conceptual variations in LMs with original LM compositions or morphologies. Such new concepts may inspire further research on LMs. Here, we summarise the conceptual variations in LMs (Fig. 4). While the LM size is usually on the millimetre scale, a recent work, displayed in Fig. 4A, reported the massive production of LMs with sizes in the range of single to hundreds of micrometres. This work allowed the isolation of a single micro-metre-sized LM, enabling micro-LM handling, as shown in Fig. 4A. It is noteworthy that a large number of such micro-

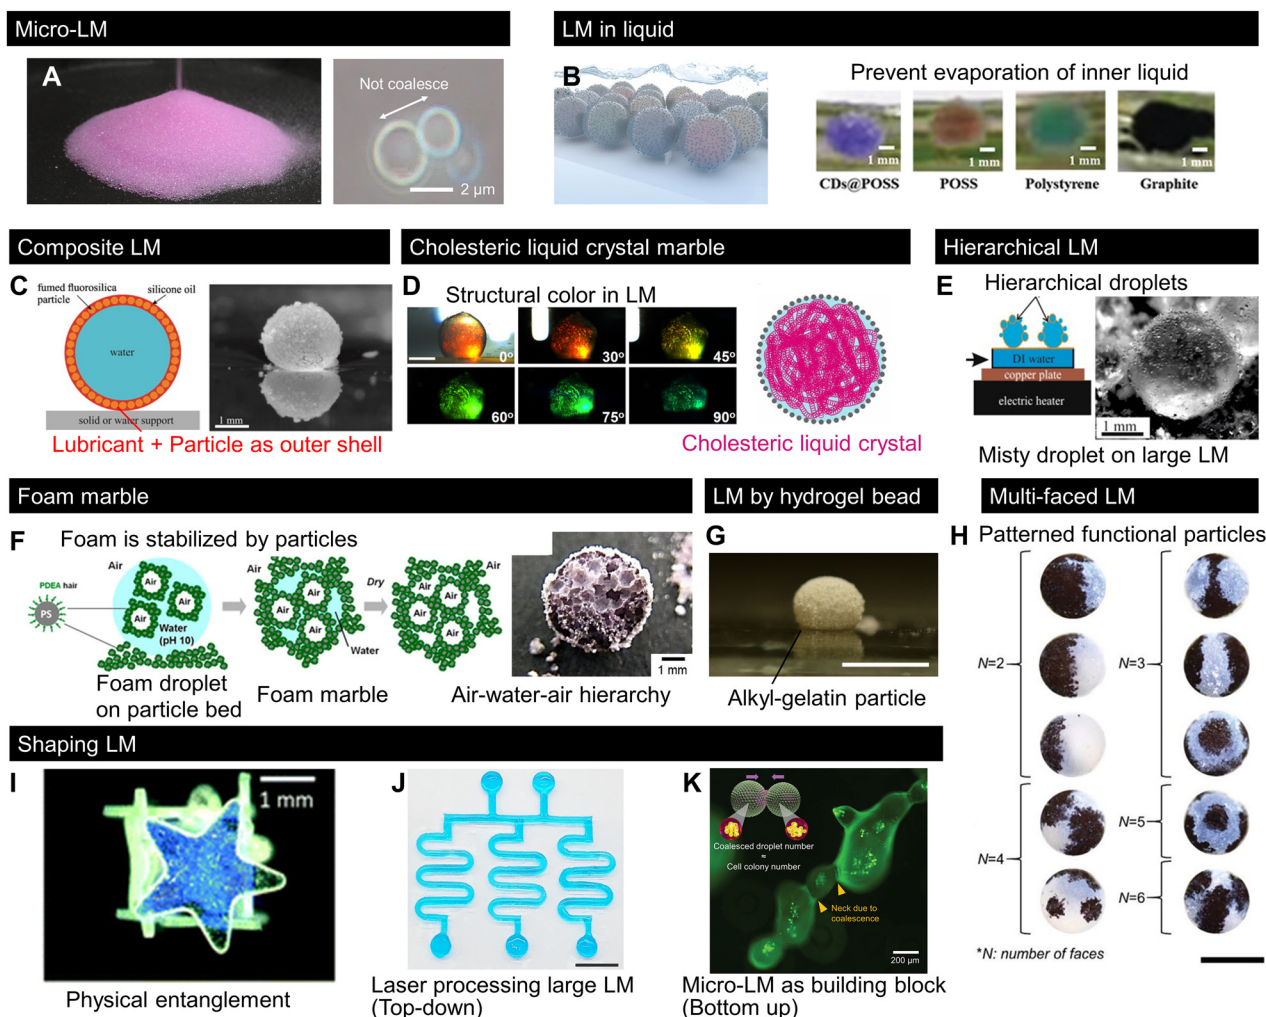


Fig. 4 Recent progress in LMs with uncommon shapes, structures, and compositions. (A) Mass LMs downsized from a single micrometre to hundreds of micrometres behave like dry powder.¹³ (B) LMs sink into an immiscible liquid pool to prevent inner liquid evaporation.⁹⁷ (C) LM covered with lubricated particles, namely composite LMs.⁹⁹ (D) LM with a cholesteric liquid crystal core exhibit a structural colour change.¹⁰³ (E) LM covered with tiny droplets, namely hierarchical LM.¹⁰⁴ (F) LM made of foam resulted in air–water–air type LM.¹⁰⁵ (G) LM composed of hydrogel particles.¹⁰⁶ (H) Particles multipatterned on droplets using a patchwork-like process.¹¹⁰ (I) LM made of a shaped solid. The physical entanglement of shaped solids deforms the droplets.¹¹³ (J) Laser-processed nonspherical millimetric LM.¹¹⁴ Scale bar: 1 cm. (K) Non-spherical micro-LMs formed by LM coalescence.¹³ Scale bar: 200 μm . Copyrights: (A) and (K) Reproduced from ref. 13 with permission from Wiley-VCH GmbH, Copyright 2023; (B) reproduced from ref. 97 with permission from Wiley-VCH GmbH, Copyright 2020; (C) reproduced from ref. 99 with permission from Elsevier, Copyright 2020; (D) reproduced from ref. 103 with permission from Wiley-VCH GmbH, Copyright 2020; (E) reproduced from ref. 104 with permission from Elsevier, Copyright 2022; (F) reproduced from ref. 105 with permission from the American Chemical Society, Copyright 2022; (G) reproduced from ref. 106 under CC BY 4.0, MDPI 2022. (H) Reproduced from ref. 110 with permission from Wiley-VCH GmbH, Copyright 2021; (I) reproduced from ref. 113 under CC BY 3.0, 2021 the Royal Society of Chemistry; (J) reproduced from ref. 114 under CC BY 4.0, 2023 Springer Nature Limited.

LMs behave like granular materials.¹³ It has been known that microdroplets are held in a hydrophobic particle network, the so-called dry liquid.^{95,96} The micro-LMs are isolated to a single droplet from the hydrophobic network in a stable state; additionally, the size of the micro-LMs is uniform after the sintering process.

4.2 Wet LMs

Although LMs are generally handled in air, the work presented in Fig. 4B reported the use of LMs in liquids.⁹⁷ LMs in liquids are analogous to Pickering emulsions that are stabilised by

particles;⁹⁸ however, marbles in the millimetric scale can be isolated and handled as single droplets. The authors showed that LMs in liquids can be used to prevent the evaporation of the LM content, which is useful for applications requiring long-term stability.

Fig. 4C shows a new concept for composite LMs in which a water droplet is covered with both an immiscible lubricant and particles.⁹⁹ Similar to the case of lubricant-infused surfaces, where a lubricant layer was stabilised by capillary interactions with the surface structures,^{100–102} in composite LMs, a stable lubricant/particle layer was formed at the interface of



remain rather simple (*e.g.*, Janus LMs; Fig. 3C).¹¹² Multi-faced LMs also provide insights for precise patterning with functional particles on the droplet, namely “multi-faced LMs”, which provides the synergetic functionality to LMs that cannot be achieved by simply mixing functional particles.

4.3 Liquid crystal marbles

Optical soft materials also benefit from the new concepts of LMs. The work presented in Fig. 4D introduced a LM with aqueous hydroxypropyl cellulose solution as the inner liquid.¹⁰³ While this may seem to be a simple variation of the inner liquid of a LM, hydroxypropyl cellulose self-assembles as a cholesteric liquid crystal in the aqueous phase. By regulating the cholesteric pitch in the LM, LMs with various structural colours were successfully fabricated. This unfamiliar photonic response of LMs contributes to variations in optically soft materials.

4.4 Hierarchical LMs

The approach presented in Fig. 4E comprises a hierarchical LM, which is covered with smaller droplets or LMs.¹⁰⁴ They can be formed by forming a particle bed at the surface of a hot water bath. Hot water vapour recondenses on the hydrophobic powder, forming LMs that then stick to neighbouring LMs, giving rise to hierarchical LMs.

While hierarchical LMs are made of different liquid parts, a recent work (Fig. 4F) demonstrated “foam” marbles comprising a hierarchical structure of LMs with alternating liquid and air contents, formed by covering the foam with hydrophobic particles.¹⁰⁵ This foam marble had a double emulsion-like feature, *i.e.*, particle-stabilised air bubble-in-liquid and liquid droplet-in-air (air/liquid/air type). After drying, the foam marbles formed porous spheres with pore sizes of tens of micrometres.

4.5 LMs by soft particles

Fig. 4G shows a LM composed of soft hydrophobic gelatine particles.¹⁰⁶ The material properties of LMs have been studied by changing their particle size, shape, and/or surface chemistry.^{20,43,107} Because recent studies have revealed that solid softness varies the interfacial energy balances, called soft wetting,^{108,109} the LM based on a soft solid provides new opportunities to explore the effects of softness on LM properties.

4.6 Multi-faced LMs

As mentioned in the fabrication section, patterning LMs with different types of particles introduces new possibilities for various applications. The work presented in Fig. 4H demonstrated the possibility of fabricating complex patchworks with different functional particles on the surface of the liquid. The fabrication procedure allows flexible engineering for a wide range of patchworks.¹¹⁰ In contrast to fluid instability, such as Rayleigh–Benard which allows the formation of complex fluid patterns, it is difficult to pattern granules because of their scale.¹¹¹ Thus, conventional patterns on the surface of LMs

4.7 Non-spherical LMs

We have shown in Fig. 2D that various granule shapes along with different droplet/granular size ratios. Small nonwetting droplets are spherical owing to surface energy minimization; however, the presence of particles at the surface of LMs allows the formation of non-spherical LMs. Fig. 4I–K illustrate different approaches used to shape LMs.^{13,113,114} The first method, presented in Fig. 4I, reported a box-shaped droplet covered with a millimetric star-shaped plate.¹¹³ Here, the plates were physically entangled with each other, making the droplets nonspherical. This concept is analogous to capillary origami¹¹⁵ or capillary containers.¹¹⁶ In this case, LM shape reconfigurability was strongly hindered; however, this LM exhibited high mechanical robustness. Li *et al.* proposed another method to deform droplets based on the interfacial jamming of nanoparticles on the droplets.¹¹⁷ Fig. 4J shows the laser-based shaping process of a large LM with a specific geometry.¹¹⁴ While the laser technique is a top-down approach for LM shaping, Fig. 4K shows a bottom-up shaping approach through the formation of non-spherical LMs by merging micro-LMs as building blocks.¹³ This method enables the fabrication of complex marbles with micrometric dimensions, such as microfiber-shaped LMs formed by the coalescence of a micro-LM line. These new concepts are expected to give rise to unexpected LM properties, systems, and applications. Finally, among the new concepts, there is an increasing interest in the mechanical properties of LMs and LM assemblies to produce more complex structures.

5. LM-templated material design

5.1 Supraparticle synthesis

Fig. 5 shows the recent advances in material design based on LMs as “templates”. The first approach displayed in Fig. 5A and B involves particle adsorption at the liquid interface as well as controlled evaporation to arrange and position particles and polymers to form complex supraparticles.^{118,119} Both methods utilise the low adhesion of the LM contact line to the substrate (Fig. 2M). The method displayed in Fig. 5A involves covering an aqueous solution of hydrophilic polymers/particles with hydrophobic particles to form a LM. Then, the inner water evaporates, and owing to the receding contact line, the inner particles/polymers become concentrated and form a complex biphilic supraparticle known as (hydrophilic)core-(hydrophobic)shell. As shown in Fig. 5B, the inner liquid content was removed *via* calcination to form hollow (air-core) supraparticles. A similar study was reported for the droplets of a colloidal dispersion deposited on a superhydrophobic surface; evaporation and the absence of contact line pinning



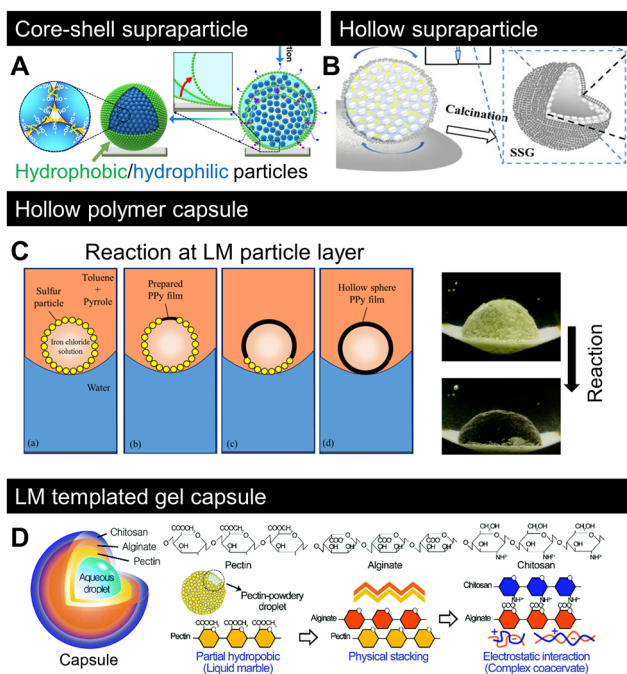


Fig. 5 Recent progress on LM-templated materials. (A) Designing core-shell or (B) hollow supraparticles by removing the inner liquid from LM.^{118,119} (C) Polymerisation of pyrrole on the LM surface by a chemical reaction between the inner liquid and surrounding media.¹²³ (D) LM-templated gel-capsule formation.¹²⁴ Copyrights: (A) Reproduced from ref. 118 under CC BY 4.0, 2023 Springer Nature Limited; (B) reproduced from ref. 119 with permission from Elsevier, Copyright 2022; (C) reproduced from ref. 123 with permission from Elsevier, Copyright 2021; (D) reproduced from ref. 124 with permission from the Royal Society of Chemistry, Copyright 2020.

allowed the formation of supraparticles.^{120–122} However, this method does not enable the formation of core-shell type supraparticles that make LMs a valuable tool for forming such complex materials.

5.2 Interfacial polymerisation

Recent studies have demonstrated that LMs can serve as intermediate templates to form polymer capsules, as shown in Fig. 5C and D.^{123,124} Fig. 5C shows that polymerisation occurred at the droplet surface. The monomer and initiator were supplied from the outer fluidic medium (in this case, toluene) and inner liquid (in this case, iron chloride). The idea of interfacial polymerisation based on LMs in air has been reported before.¹²⁵ However, the reaction occurs at the liquid-liquid interface, *i.e.*, LMs in the liquid system (Fig. 4B) form a hollow polymeric sphere. As shown in Fig. 5D, LMs stabilised by pectin powder were physically stacked with alginate and then electrostatically covered with chitosan to form a polyion complex-like physical gel capsule. These studies demonstrated that LMs are flexible templates for designing complex materials. Although the products are limited to spherical LMs, recent advances in the shaping of non-spherical LMs (Fig. 4I–K) should enable the formation of templates for non-spherical materials.

6. Recent lab-in-a-marble applications

6.1 Lab-in-a-marble (LIAM)

We now discuss the recent cutting-edge LM applications. Several studies have attempted to conduct laboratory experiments such as material synthesis, analysis, and bio-culturing on a small scale. Owing to the advances in microfluidics through the concept of “lab-on-a-chip”,¹²⁶ which is beneficial for waste reduction (both liquid and equipment) through miniaturisation, this domain has been strongly developed in recent years. While recent microfluidic devices have many gimmicks for complex material synthesis and analysis, they require the formation of specific fine microfluidic channels through dry processing and the use of high injection pressure to pump fluids.¹²⁷ Moreover, the wastage of processed channels may lead to an environmental burden. Recently, the research field studying microfluidics and fluid-structure interactions, namely micro elastofluidics, has greatly developed.¹²⁸ In elastofluidics, LMs are waste-free fluidic systems owing to their recyclable outer particles and non-spilt inner liquid. Thus, it can be potentially used in a new class of laboratory experiments at the droplet scale with applications similar to that of microfluidic devices, known as “lab-in-a-marble (LIAM)”. Various applications based on LMs have been reported thus far, including reactions, analysis, sensing, and energy conversion.^{129,130}

6.2 Design strategies

The typical LIAM strategies are summarised in Fig. 6A and B. As exemplified by microfluidics, droplet-scale lab analysis first requires displacing and bringing several chemical species or biomaterials in contact with each other, which is one of the features of LMs owing to their low friction and coalescence capability. Additionally, to further process the liquid content, the liquid must be divided into smaller volumes to enable different characterisations or parallelise the subsequent steps of the process. This is also possible in LMs owing to their reconfiguration capabilities, because of which they can be easily split into sub-LMs. In addition to the fluid manipulation capabilities of LMs, Fig. 6A describes LM-specific advantages for a droplet-scale laboratory. While LMs can be used as standard microchemical reactors by merging the content of two LMs, the outer hydrophobic particles, whose primary function is to stabilise the liquid, can also be used to modify the reactor capabilities of LMs. Some studies have demonstrated the use of specific particles to assist reactions owing to their catalytic or reactive properties.^{91,131} Moreover, in contrast to microfluidics, where droplets are enclosed inside liquid and solid channels, the open geometry and porous particle interface enable the use of a wider range of stimuli with LMs. For example, gaseous chemicals, light, and heat sources can be employed to trigger and/or enhance reactions inside LMs.^{64,132} This sensitivity to stimuli may be related to the density and thickness of LMs.



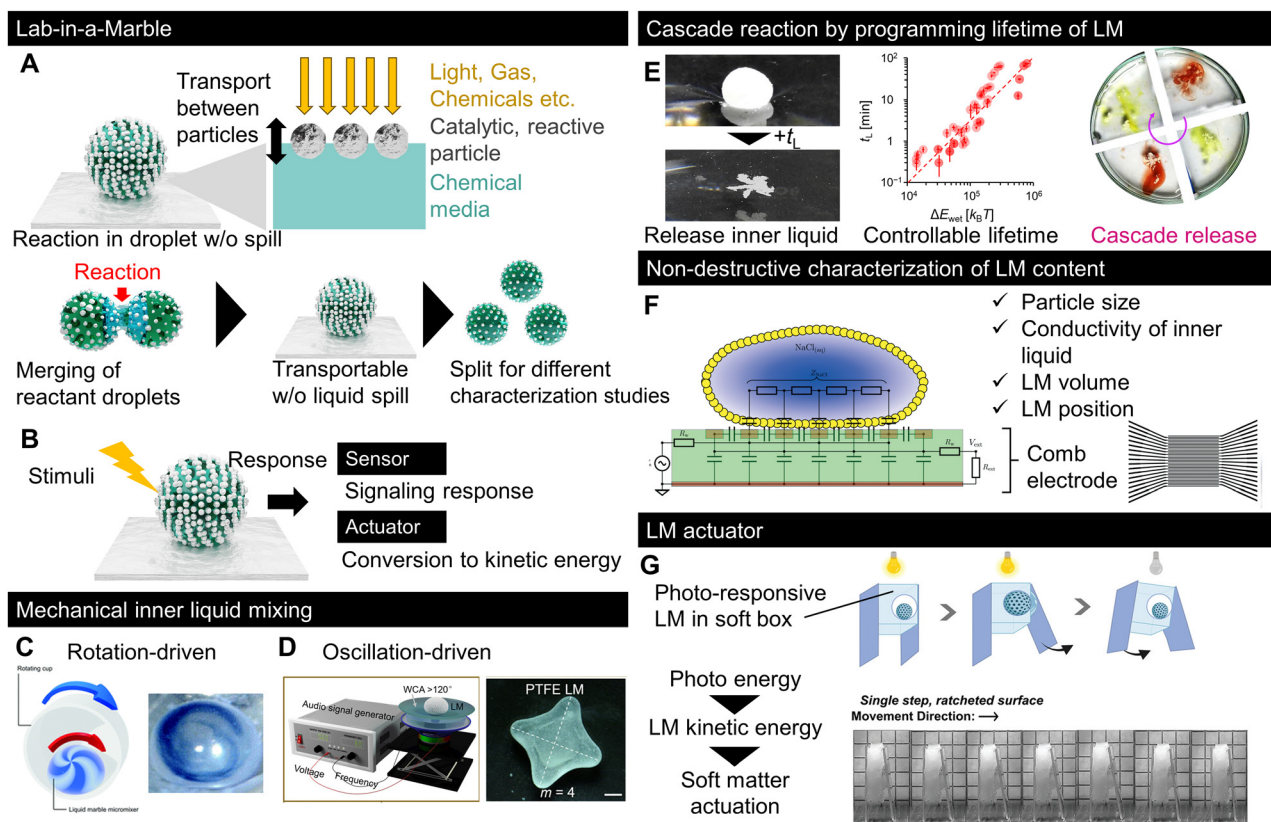


Fig. 6 Recent progress in LM for microreactors, sensors, and actuators. Typical strategies for using LMs as (A) reactors, or (B) sensors and actuators.^{138,139} The inner liquid is mixed by LM using (C) rotation or (D) oscillation. (E) Cascade chemical reaction using LM with a preprogrammed lifetime on a liquid pool.¹⁴⁰ (F) Contactless detection of LM properties by electroanalysis using a comb electrode.¹⁴¹ (G) LM-based actuator. The photoresponsive motion of LM was used to actuate the locomotion of soft objects.¹⁴² Copyrights: (C) Reproduced from ref. 138 with permission from the Royal Society of Chemistry, Copyright 2022; (D) reproduced from ref. 139 with permission from the American Chemical Society, Copyright 2022; (E) reproduced from ref. 140 with permission from Wiley-VCH GmbH, Copyright 2023; (F) reproduced from ref. 141 with permission from the Royal Society of Chemistry, Copyright 2019; (G) reproduced from ref. 142 with permission from Wiley-VCH GmbH, Copyright 2023.

LMs can also be used as sensors or actuators, as shown in Fig. 6B; in this strategy, a responsive species is used as either a particle or within an inner liquid. If a responsive LM is used to quantify, visualise, or detect stimuli, and then the LM works as a sensor. For example, LMs can be used as gas-sensing devices by loading them with a pH-sensitive solution, which changes colour in response to acidic or basic chemicals.^{133,134} If the LM response to external stimuli is converted to kinetic energy, it functions as an actuator to transport liquids or pick up particles. Owing to their reconfigurable features, LM actuators can be used in soft robotic systems.¹³⁵

6.3 Chemical reactors

Although various LM reviews have focused on LM applications,^{10,136,137} we selected recent reports with unfamiliar insights into LM applications. While coalescence-based chemical reactions have been reported, the miniaturisation of LMs makes effective mixing methods between the reactants more important because the viscosity action dominates at a small scale. Fig. 6C and D show the LM mixing methods;^{138,139} both studies successfully generated a flow designed to mix the

inner liquid *via* outer mechanical stimulation through rotation or oscillation.

6.4 Cascade reactions

While the LM content can be retrieved by a simple mechanical action, it is important to control its lifetime for liquid release. Recently, researchers successfully engineered particles to control the LM

lifetime in a liquid pool while remaining stable upon being deposited on a substrate.¹⁴⁰ The floating lifetime of LM is controlled by forming marbles with a particle layer made of nano-clays with different surface chemistries. By loading chemicals into floating LMs with different lifetimes, the encapsulated chemicals are released into the liquid pool with programmed timing, followed by cascade reactions, as shown in Fig. 6E.

6.5 Non-destructive LM sensing

The characterisation of LMs is important for applications, as shown in Fig. 6F, which focuses on sensing LM properties, including the particle size, liquid conductivity, volume, and



position.¹⁴¹ The properties of LMs were detected using a comb electrode that measured the electrical response.

6.6 LM-based actuators

More original concepts based on LMs have recently been published, as shown in Fig. 6G, which displays the concept of robotic actuation driven by photo stimuli.¹⁴² In this study, the photo-stimulated kinetic energy of LMs was used as the engine of a small robot to achieve photo-responsive locomotion. LMs operated as tiny kinetic energy converters. Although the conversion efficiency was not reported, this work demonstrated the potential of complex robotic systems.

6.7 Bioapplications

The physicochemical properties and structural uniqueness of LMs have attracted the interest of many scientists and demonstrated potential for bioapplications in addition to the aforementioned microfluidics, sensors, and actuators. Here, we present some examples of bioapplications based on LMs over the past few years on multiscale biological specimens ranging from nucleic acids and proteins to cells and mini-organs, and discuss the advantages of LMs over conventional methods (Fig. 7).

6.8 SERS detection

Noncovalent interactions play an important role in biological phenomena such as enzyme–substrate, DNA–drug, and host–pathogen interactions. Leong *et al.* fabricated plasmonic LMs consisting of Ag nanocubes functionalised with mercaptobenzoic acid (MBA) as a surface-enhanced Raman scattering (SERS) platform (Fig. 7A).¹⁴³ MBA immobilised on Ag nanocubes served as an interaction probe molecule; moreover, hydrogen bonding and ionic interactions with the carboxyl groups of MBA resulted in differences in the Raman spectra. Although conventional SERS studies are limited to detecting a single mode of interaction, the combination of plasmonic LMs with chemometrics and density functional theory enables the observation of multiple molecular interactions and successfully demonstrates that noncovalent intermolecular interactions with nucleotide bases can be detected *in situ*.

6.9 DNA amplification

Because typical LMs lack appropriate heating capabilities, their applications as reactors or in analytical fields are limited to room temperature or using heating equipment. Fe₃O₄ nanocube-coated LMs have been fabricated as heatable miniature reactors because their internal liquid phase can be uniformly heated when exposed to an alternating magnetic field (AMF).¹⁴⁴ Furthermore, because Fe₃O₄ nanocube-coated LMs allowed the desired temperature and heating/cooling program by the power and on/off switching of the AMF, they were applied as a miniature reactor for DNA amplification and achieved 25% better amplification compared to commercially available thermal cycling methods (Fig. 7B). Although photo-thermal LMs, wherein only the light-irradiated area is heated, have been reported, the use of the magnetothermal effect in

Fe₃O₄ nanocube-coated LMs results in more uniform heating and is expected to be used as a larger-scale reactor.

6.10 Protein analysis

LMs are promising not only as reactors for miniaturised biochemical reactions but also as platforms for protein analysis. Typical protein analyses require pretreatment owing to the complexity of samples, which is difficult to accomplish with simple LMs. However, Niu *et al.* addressed this problem by designing fluidic channels using deformable LMs, termed liquid plasticine (Fig. 7C).¹⁴⁵ Liquid plasticine takes advantage of the high structural and morphological flexibility of LMs; thus, it can be shaped into rod-like shapes that mimic channels. Using human serum samples, they successfully demonstrated that the combination of liquid plasticine-based channels and isoelectric focusing (IEF) can simultaneously accomplish the important pretreatment steps of protein separation and enrichment. After pretreatment with IEF, LMs containing proteins of interest were isolated by cutting the liquid plasticine, allowing further evaluation by colorimetry and mass spectrometry.

6.11 Cell cryopreservation

In addition to biomolecules such as nucleic acids and proteins, as described above, biological samples with larger sizes, such as cells, can be confined to the liquid phase of LMs. Liu *et al.* proposed a LM-based cell cryopreservation method (Fig. 7D).¹⁴⁶ They fabricated LMs composed of gelatine solution and hydrophobic PTFE powder, where the PTFE particle layer not only acted as a physical barrier to protect cells from the external environment, but also influenced ice formation and growth during the freeze–thaw process of the solution. Furthermore, LMs containing gelatine in the liquid phase do not require additives, such as dimethyl sulfoxide (DMSO), which is cytotoxic, and foetal bovine serum (FBS), which may cause pathogenic contamination, like conventional cell cryopreservation; gentle shaking immediately destroys LMs and allows recovery of cells, thereby achieving high cell viability after cryopreservation.

6.12 Single-cell picking

Recently, a cell-manipulation technique based on dry cells: cell-encapsulated micro-LMs, obtained by simply spraying a cell suspension onto a powder bed of hydrophobic fumed silica nanoparticles, was developed.¹³ The number of cells to be encapsulated was determined by adjusting the size of LMs and the concentration of the cell suspension; accordingly, dry micrometre-sized cells were fabricated. These dry cells provided a venue for the isolation of single cells and observation of their cellular phenomena, such as migration and growth, in addition to utilising LMs as simple storage containers for cells (Fig. 7E). Cells sequestered under dry conditions showed a cell viability of approximately 90% for at least three days. The cellular phenomena can be analysed for longer periods owing to handling techniques such as changing the internal liquid (culture medium). Furthermore, by using the conditions of dry-cell formation and physical properties originating from



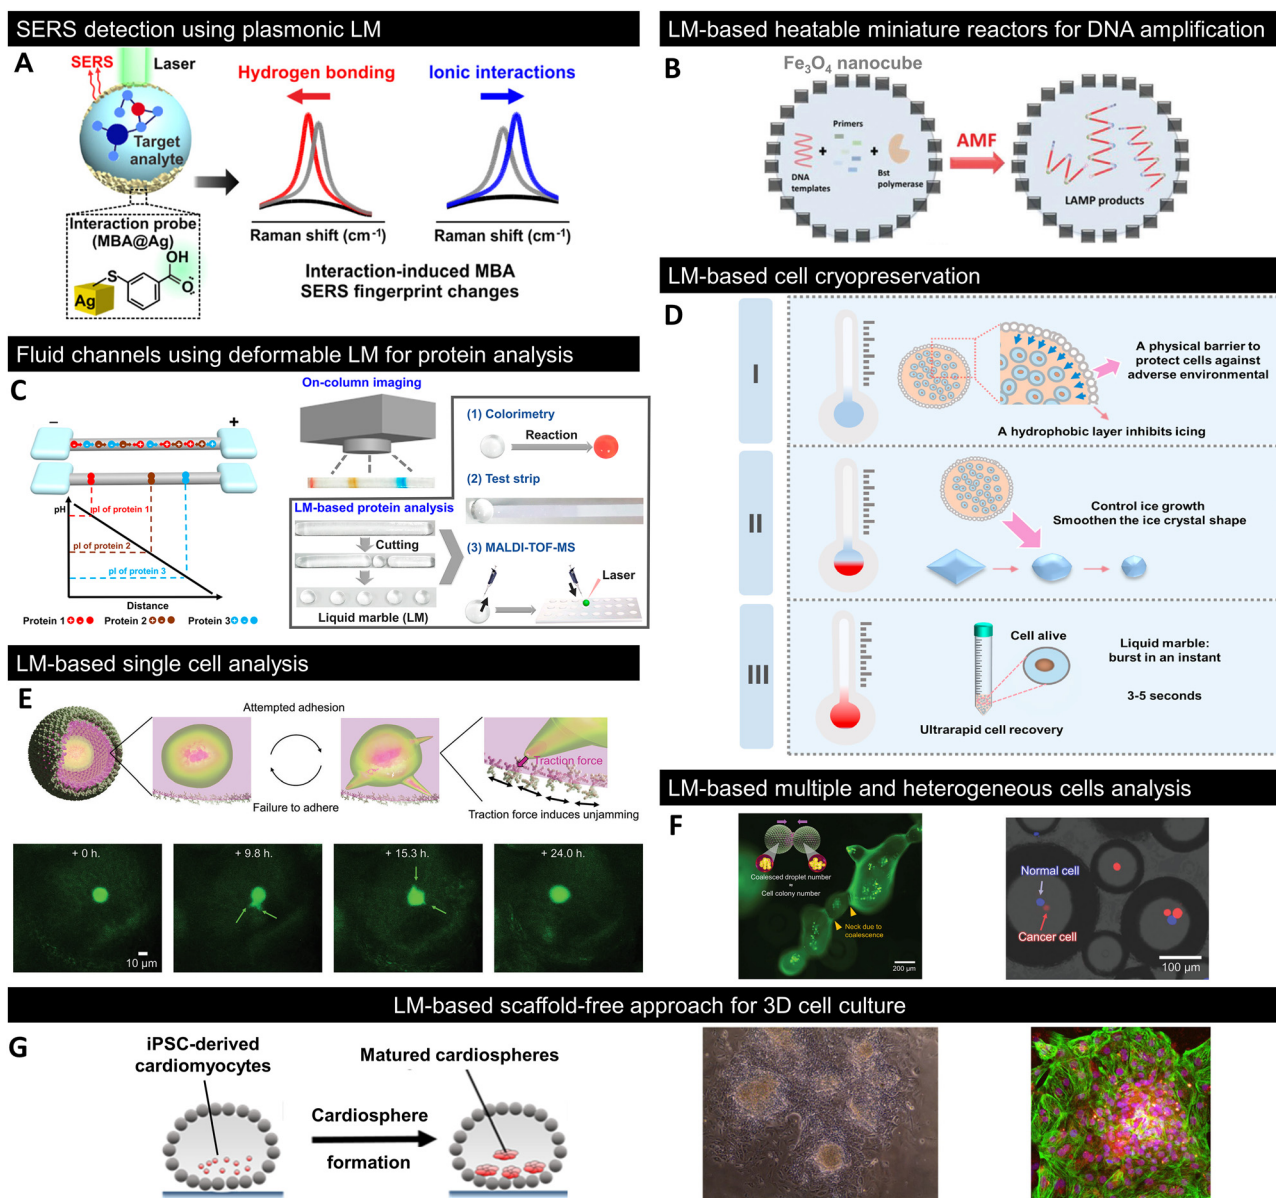


Fig. 7 Recent progress in LM for bioapplications. (A) *In situ* detection of noncovalent intermolecular interactions between MBA and the target analyte using plasmonic LMs.¹⁴³ (B) DNA amplification using Fe₃O₄ nanocube-coated LMs as an alternative magnetic field (AMF)-triggered heatable miniature reactors.¹⁴⁴ (C) Isoelectric focusing (IEF)-based protein analysis using fluid channels composed of deformable LM, termed liquid plasticine.¹⁴⁵ (D) Cryopreservation of cells using gelatine-based LMs and its mechanism.¹⁴⁶ DryCell technology is based on cell-suspension microscale LMs for the analysis and manipulation of (E) single and (F) multiple heterogeneous cells.¹³ (G) LM-based scaffold-free bioreactor for the 3D culture of *in vitro* derived human cardiomyocytes.¹⁵⁰ Copyrights: (A) Reproduced from ref. 143 with permission from the American Chemical Society, Copyright 2020; Copyrights: (B) reproduced from ref. 144 with permission from Wiley-VCH GmbH, Copyright 2021; Copyrights: (C) reproduced from ref. 145 with permission from the American Chemical Society, Copyright 2020; Copyrights: (D) reproduced from ref. 146 with permission from Elsevier, Copyright 2022; Copyrights: (E) and (F) reproduced from ref. 13 with permission from Wiley-VCH GmbH, Copyright 2023; Copyrights: (G) reproduced from ref. 150 with permission from Elsevier, Copyright 2020.

LMs, various cellular environments can be created, including spatially arranged cell colonies induced by fusion and one-cell confinement of different cell types (Fig. 7F).

6.13 Three-dimensional cell culturing

Three-dimensional (3D) cell cultures more accurately mimic the *in vivo* environment and have several advantages over con-

ventional two-dimensional (2D) culture systems. Hence, studies have been conducted to utilise the liquid phase of LMs surrounded by a hydrophobic powder as an *in vitro* 3D culture field. Cells in the liquid phase of LMs tend to self-assemble to form spheroid- and organoid-like structures, which have been observed in C6 rat gliomas, human mammary fibroblasts, and human hepatocellular carcinoma cells.^{147–149} Aalders *et al.*



were the first to apply LMs to the 3D culture of induced pluripotent stem cell (iPSC)-derived cardiomyocytes and succeeded in forming cardiomyocytes in less than 24 hours (Fig. 7G).¹⁵⁰ Cardiospheres formed inside LMs also expressed myocardial markers similar to those in conventional 2D culture systems. Further findings in LM-based 3D culture systems could provide a useful alternative to expensive and experienced scaffold-free 3D culture methods such as spinner flasks and hanging drops.

7. Conclusions

In this review, we comprehensively highlighted the recent progress in LMs. This literature review revealed that the latest research on LMs extends far beyond mere applications or novel particle/liquid combinations. Indeed, there is flourishing literature dedicated to new LM concepts, LM formation methods, understanding of LM physical properties, and LM-templated material design. The richness of the literature and emergence of several new LM concepts foreshadow the strong and rapid development in the LM field. In the fundamental physical analysis of LMs, the comparison of the mechanics and phase invasion behaviour between the droplet and LM offered us the opportunity to reconsider the physical properties of LMs. Moreover, while the initial LMs are conceptually similar to drops on superhydrophobic surfaces, the physical properties of new conceptual LMs are yet to be investigated. On the industrial side, the large-scale and reliable production of LMs remains a bottleneck. The recently developed LM formation method can largely solve this issue, making LMs more applicable in industries. Moreover, because the different fabrication processes of conventional LMs lead to a wide range of new LM concepts, we can expect the recently proposed fabrication process to bring its own variations, which will further broaden LM variations. The new LM concepts must expand the potential use of LMs. Non-spherical LMs can expand the use of LIAM to enable the design of complex systems, such as microfluidic devices, and hierarchical LMs or LM patchworks can be used to design new LM-templated materials. Focusing on LM applications, various advances in responsive LMs, evaluation methods, and energy conversion systems have been proposed, thus broadening the applicability of LMs. From the perspective of materials science, evolutive LMs can adapt their properties to resist their environment because recent research directions in materials science have shifted from simple responsive materials to designing adaptive or interactive materials similar to living objects, which are much more complex than responsive or intelligent materials and have gained considerable attention.¹⁵¹ For example, a recently developed supermolecular chemistry-enabled self-training gel increases its tensile strength with breakage–healing cycles similar to that of muscle.¹⁵² Thus far, responsive LMs have been studied mainly in the 2010s,¹⁶ and in the future, LMs should be designed to have adaptive capacities. This may be achieved

by liquid and particle engineering, which may help in obtaining LMs with fine-tuned responses to the environment. One may think that to design multiple liquids or particles, a cascade response or multilevel stability may be required. As discussed in multi-faced LMs, tuneable multi-responsivity can be achieved by combining multi-functional particles. The mixing ratio of several functional particles would likely be the key factor to achieve tuneable multi-functionality in LMs. Moreover, keywords used in LMs such as “reconfigurability” and “jamming transition” are included in designing recent adaptive materials systems.^{153,154} For example, utilizing liquid reconfigurability, the concept of liquid-based adaptive structural materials (LASMs) has been recently proposed.¹⁵⁵ Thus, we believe that adaptive LMs can be designed by focusing on shape reconfigurability and interfacial jamming in LMs. The diversity of hydrophobic particles and liquid phases that constitute LMs has led to the design and development of various functional LMs for bioapplications that are challenging for conventional microfluidics systems. LMs can contain biological specimens of various sizes within a specific liquid space separated from the external environment, enabling the analysis of noncovalent intermolecular interactions, DNA amplification reactions, and rapid protein analysis. In addition to using LMs as miniaturized containers for biochemical reactions and storage containers for biological samples, they can be used to culture and maintain living organisms such as cells. In particular, single-cell analysis technologies that measure the genome, epigenome, transcriptome, proteome, and metabolome for each single cell have recently attracted significant attention to accurately understand single-cell level behaviour in the cellular society of embryogenesis, tissues, and organs. Because individual elemental technologies for bio-analysis, cell manipulation, and 3D culture for spheroid and mini-organ formation have already been established using LMs, the realisation of bioapplications using LIAM that integrate everything, from cell culture to analysis, would not be far off.

Author contributions

Mizuki Tenjimbayashi: project administration, supervision, conceptualization, investigation, visualization, writing – original draft, validation, and funding acquisition. Timothée Mouterde: supervision, conceptualization, visualization, writing – original draft, validation, and funding acquisition. Pritam Kumar Roy: investigation, visualization, writing – original draft, and validation. Koichiro Uto: investigation, visualization, writing – original draft, and validation.

Conflicts of interest

There are no conflicts to declare.



Acknowledgements

MT, TM, and KU acknowledge the support from TIA-Kakehashi. PKR is a JSPS International Research Fellow (Postdoctoral Fellowships for Research in Japan (Standard)). TM and PKR gratefully acknowledge the financial support provided by the Japan Society for the Promotion of Science (JSPS).

References

- 1 T. G. Benton and W. A. Foster, *Proc. R. Soc. B*, 1992, **247**, 199–202.
- 2 P. Aussillous and D. Quéré, *Nature*, 2001, **411**, 924–927.
- 3 Y. Xue, H. Wang, Y. Zhao, L. Dai, L. Feng, X. Wang and T. Lin, *Adv. Mater.*, 2010, **22**, 4814–4818.
- 4 E. Bormashenko, *Langmuir*, 2017, **33**, 663–669.
- 5 L. Gao and T. J. McCarthy, *Langmuir*, 2007, **23**, 10445–10447.
- 6 V. Sivan, S.-Y. Tang, A. P. O'Mullane, P. Petersen, N. Eshtiaghi, K. Kalantar-zadeh and A. Mitchell, *Adv. Funct. Mater.*, 2013, **23**, 144–152.
- 7 D. Foresti, K. T. Kroll, R. Amissah, F. Sillani, K. A. Homan, D. Poulikakos and J. A. Lewis, *Sci. Adv.*, 2018, **4**, eaat1659.
- 8 D. Broboana, A.-M. Bratu, I. Magos, C. Patrascu and C. Balan, *Sci. Rep.*, 2022, **12**, 1774.
- 9 G. McHale and M. I. Newton, *Soft Matter*, 2011, **7**, 5473.
- 10 N. M. Oliveira, R. L. Reis and J. F. Mano, *Adv. Healthcare Mater.*, 2017, **6**, 1700192.
- 11 Y. Feng, G. Liu, J. Xu, K. Wang, W. Mao and G. Yao, *Langmuir*, 2022, **38**, 2055–2065.
- 12 Y. Feng, L. Wang, J. Xu and G. Liu, *Soft Matter*, 2022, **18**, 5230–5238.
- 13 M. Tenjimbayashi, S. Yamamoto and K. Uto, *Adv. Mater.*, 2023, **35**, 2300486.
- 14 J. Saczek, X. Yao, V. Zivkovic, M. Mamlouk, D. Wang, S. S. Pramana and S. Wang, *Adv. Funct. Mater.*, 2021, **31**, 2011198.
- 15 M. Tenjimbayashi and S. Fujii, *Small*, 2021, **17**, 2102438.
- 16 S. Fujii, S. Yusa and Y. Nakamura, *Adv. Funct. Mater.*, 2016, **26**, 7206–7223.
- 17 Y. Wang, K. Ma and J. H. Xin, *Adv. Funct. Mater.*, 2018, **28**, 1705128.
- 18 M. Tenjimbayashi, S. Samitsu and M. Naito, *Adv. Funct. Mater.*, 2019, **29**, 1900688.
- 19 E. Bormashenko, R. Balter and D. Aurbach, *J. Colloid Interface Sci.*, 2012, **384**, 157–161.
- 20 B. P. Binks and R. Murakami, *Nat. Mater.*, 2006, **5**, 865–869.
- 21 B. T. Lobel, C. A. Thomas, P. M. Ireland, E. J. Wanless and G. B. Webber, *Adv. Powder Technol.*, 2021, **32**, 1823–1832.
- 22 Y. Zhang, H. Cui, B. P. Binks and H. C. Shum, *Langmuir*, 2022, **38**, 9721–9740.
- 23 T. Onda, S. Shibuichi, N. Satoh and K. Tsujii, *Langmuir*, 1996, **12**, 2125–2127.
- 24 T. Sun, L. Feng, X. Gao and L. Jiang, *Acc. Chem. Res.*, 2005, **38**, 644–652.
- 25 P. Jin, K. Zhao, Z. Blin, M. Allais, T. Mousterde and D. Quéré, *J. Chem. Phys.*, 2023, **158**, 204709.
- 26 P. Aussillous and D. Quéré, *Proc. R. Soc. A*, 2006, **462**, 973–999.
- 27 G. McHale and M. I. Newton, *Soft Matter*, 2015, **11**, 2530–2546.
- 28 V. N. Paunov, *Langmuir*, 2003, **19**, 7970–7976.
- 29 N. Vogel, J. Ally, K. Bley, M. Kappl, K. Landfester and C. K. Weiss, *Nanoscale*, 2014, **6**, 6879–6885.
- 30 G. Gillies, M. Kappl and H.-J. Butt, *Adv. Colloid Interface Sci.*, 2005, **114**, 165–172.
- 31 D. Zang, Z. Chen, Y. Zhang, K. Lin, X. Geng and B. P. Binks, *Soft Matter*, 2013, **9**, 5067.
- 32 C. H. Ooi, C. Plackowski, A. V. Nguyen, R. K. Vadivelu, J. A. St. John, D. V. Dao and N.-T. Nguyen, *Sci. Rep.*, 2016, **6**, 21777.
- 33 T. Arbatan and W. Shen, *Langmuir*, 2011, **27**, 12923–12929.
- 34 E. Bormashenko, R. Pogreb, G. Whyman and A. Musin, *Colloids Surf., A*, 2009, **351**, 78–82.
- 35 E. Bormashenko, R. Pogreb, G. Whyman, A. Musin, Y. Bormashenko and Z. Barkay, *Langmuir*, 2009, **25**, 1893–1896.
- 36 U. Cengiz and H. Y. Erbil, *Soft Matter*, 2013, **9**, 8980.
- 37 X. Li, R. Wang, S. Huang, Y. Wang and H. Shi, *Soft Matter*, 2018, **14**, 9877–9884.
- 38 E. Bormashenko, A. Musin, G. Whyman, Z. Barkay, A. Starostin, V. Valtsifer and V. Strelnikov, *Colloids Surf., A*, 2013, **425**, 15–23.
- 39 R. Wang and X. Li, *Powder Technol.*, 2020, **367**, 608–615.
- 40 A. F. Stalder, T. Melchior, M. Müller, D. Sage, T. Blu and M. Unser, *Colloids Surf., A*, 2010, **364**, 72–81.
- 41 E. Bormashenko, *Curr. Opin. Colloid Interface Sci.*, 2011, **16**, 266–271.
- 42 F. Celestini and E. Bormashenko, *J. Colloid Interface Sci.*, 2018, **532**, 32–36.
- 43 Y. Asaumi, M. Rey, K. Oyama, N. Vogel, T. Hirai, Y. Nakamura and S. Fujii, *Langmuir*, 2020, **36**, 13274–13284.
- 44 R. Mayne, T. C. Draper, N. Phillips, J. G. H. Whiting, R. Weerasekera, C. Fullarton, B. P. J. de Lacy Costello and A. Adamatzky, *Langmuir*, 2019, **35**, 13182–13188.
- 45 T. H. Nguyen, K. Hapgood and W. Shen, *Chem. Eng. J.*, 2010, **162**, 396–405.
- 46 P. McEleney, G. M. Walker, I. A. Larmour and S. E. J. Bell, *Chem. Eng. J.*, 2009, **147**, 373–382.
- 47 Z. Liu, Y. Zhang, C. Chen, T. Yang, J. Wang, L. Guo, P. Liu and T. Kong, *Small*, 2018, 1804549.
- 48 B. T. Lobel, J. Fujiwara, S. Fujii, C. A. Thomas, P. M. Ireland, E. J. Wanless and G. B. Webber, *Mater. Adv.*, 2020, **1**, 3302–3313.
- 49 F. Geyer, Y. Asaumi, D. Vollmer, H. Butt, Y. Nakamura and S. Fujii, *Adv. Funct. Mater.*, 2019, **29**, 1808826.
- 50 M. Tenjimbayashi, Y. Watanabe, Y. Nakamura and M. Naito, *Adv. Mater. Interfaces*, 2020, **7**, 2000160.



- 51 D. Bartolo, F. Bouamrine, É. Verneuil, A. Buguin, P. Silberzan and S. Moulinet, *Europhys. Lett.*, 2006, **74**, 299–305.
- 52 M. Reyssat, A. Pépin, F. Marty, Y. Chen and D. Quéré, *Europhys. Lett.*, 2006, **74**, 306–312.
- 53 K. Wang and W. Sun, *J. Eng. Mech.*, 2015, **143**, B4015004.
- 54 T. Mouterde, P. S. Raux, C. Clanet and D. Quéré, *Proc. Natl. Acad. Sci. U. S. A.*, 2019, **116**, 8220–8223.
- 55 D. Richard and D. Quéré, *Europhys. Lett.*, 1999, **48**, 286–291.
- 56 L. Mahadevan and Y. Pomeau, *Phys. Fluids*, 1999, **11**, 2449–2453.
- 57 J. Huang, Z. Wang, H. Shi and X. Li, *Soft Matter*, 2020, **16**, 4632–4639.
- 58 H. Y. Erbil, *Adv. Colloid Interface Sci.*, 2012, **170**, 67–86.
- 59 C. H. Ooi and N.-T. Nguyen, *Microfluid. Nanofluid.*, 2015, **19**, 483–495.
- 60 M. Dandan and H. Y. Erbil, *Langmuir*, 2009, **25**, 8362–8367.
- 61 G. McHale, N. J. Shirtcliffe, M. I. Newton, F. B. Pyatt and S. H. Doerr, *Appl. Phys. Lett.*, 2007, **90**, 054110.
- 62 A. Tosun and H. Y. Erbil, *Appl. Surf. Sci.*, 2009, **256**, 1278–1283.
- 63 C. H. Ooi, E. Bormashenko, A. V. Nguyen, G. M. Evans, D. V. Dao and N.-T. Nguyen, *Langmuir*, 2016, **32**, 6097–6104.
- 64 P. S. Bhosale, M. V. Panchagnula and H. A. Stretz, *Appl. Phys. Lett.*, 2008, **93**, 034109.
- 65 B. Laborie, F. Lachaussee, E. Lorenceau and F. Rouyer, *Soft Matter*, 2013, **9**, 4822.
- 66 A. Gallo, F. Tavares, R. Das and H. Mishra, *Soft Matter*, 2021, **17**, 7628–7644.
- 67 Y. Pan, K. Shi, X. Duan and G. F. Naterer, *Int. J. Heat Mass Transfer*, 2019, **129**, 953–964.
- 68 A. G. Marín, O. R. Enríquez, P. Brunet, P. Colinet and J. H. Snoeijer, *Phys. Rev. Lett.*, 2014, **113**, 054301.
- 69 Y. Zhao, C. Yang and P. Cheng, *Appl. Phys. Lett.*, 2021, **118**, 141602.
- 70 X. Zhang, X. Liu, J. Min and X. Wu, *Appl. Therm. Eng.*, 2019, **147**, 927–934.
- 71 A. Starostin, V. Strelnikov, L. A. Dombrovsky, S. Shoval and E. Bormashenko, *Colloids Surf., A*, 2022, **636**, 128125.
- 72 X. Lin, W. Ma, L. Chen, L. Huang, H. Wu and A. Takahara, *RSC Adv.*, 2019, **9**, 34465–34471.
- 73 P. K. Roy, I. Legchenkova, S. Shoval, L. A. Dombrovsky and E. Bormashenko, *J. Colloid Interface Sci.*, 2021, **592**, 167–173.
- 74 B. Wang, K. F. Chan, F. Ji, Q. Wang, P. W. Y. Chiu, Z. Guo and L. Zhang, *Adv. Sci.*, 2019, **6**, 1802033.
- 75 P. K. Roy, M. Frenkel, I. Legchenkova, S. Shoval, B. P. Binks and E. Bormashenko, *J. Phys. Chem. C*, 2020, **124**, 9345–9349.
- 76 P. K. Roy, S. Shoval, S. Fujii and E. Bormashenko, *J. Colloid Interface Sci.*, 2023, **630**, 685–694.
- 77 P. K. Roy, I. Legchenkova, S. Shoval and E. Bormashenko, *J. Phys. Chem. C*, 2021, **125**, 1414–1420.
- 78 E. Bormashenko, P. K. Roy, S. Shoval and I. Legchenkova, *Condens. Matter*, 2020, **5**, 62.
- 79 A. T. Tyowua and A. I. Ezekwuaku, *Colloids Surf., A*, 2021, **629**, 127386.
- 80 T. Braniste, V. Ciobanu, F. Schütt, H. Mimura, S. Raevschi, R. Adelung, N. M. Pugno and I. Tiginyanu, *Materials*, 2021, **14**, 5086.
- 81 E. Bormashenko, Y. Bormashenko, R. Gryniov, H. Aharoni, G. Whyman and B. P. Binks, *J. Phys. Chem. C*, 2015, **119**, 9910–9915.
- 82 M. J. Kreder, J. Alvarenga, P. Kim and J. Aizenberg, *Nat. Rev. Mater.*, 2016, **1**, 15003.
- 83 M. Tenjimbayashi and K. Manabe, *Sci. Technol. Adv. Mater.*, 2022, **23**, 473–497.
- 84 H. Saini, P. Kallem, E. Otyepková, F. Geyer, A. Schneemann, V. Ranc, F. Banat, R. Zbořil, M. Otyepka, R. A. Fischer and K. Jayaramulu, *J. Mater. Chem. A*, 2021, **9**, 23651–23659.
- 85 P. M. Ireland, C. A. Thomas, B. T. Lobel, G. B. Webber, S. Fujii and E. J. Wanless, *J. Phys.: Conf. Ser.*, 2019, **1322**, 012006.
- 86 C. P. Whitby, X. Bian and R. Sedev, *Soft Matter*, 2012, **8**, 11336.
- 87 M. Tenjimbayashi, *Appl. Phys. Lett.*, 2023, **122**, 251604.
- 88 B. S. Lekshmi and S. N. Varanakkottu, *Langmuir*, 2022, **38**, 11743–11752.
- 89 B. S. Lekshmi, A. S. Yadav, P. Ranganathan and S. N. Varanakkottu, *Langmuir*, 2020, **36**, 15396–15402.
- 90 P. K. Roy, B. P. Binks, S. Shoval, L. A. Dombrovsky and E. Bormashenko, *Colloids Surf., A*, 2022, **649**, 129453.
- 91 Y.-E. Miao, H. K. Lee, W. S. Chew, I. Y. Phang, T. Liu and X. Y. Ling, *Chem. Commun.*, 2014, **50**, 5923–5926.
- 92 V. Lotito and T. Zambelli, *Adv. Colloid Interface Sci.*, 2022, **299**, 102538.
- 93 U. Ulusoy, *Minerals*, 2023, **13**, 91.
- 94 J. Fujiwara, F. Geyer, H. Butt, T. Hirai, Y. Nakamura and S. Fujii, *Adv. Mater. Interfaces*, 2020, **7**, 2001573.
- 95 B. P. Binks, S. K. Johnston, T. Sekine and A. T. Tyowua, *ACS Appl. Mater. Interfaces*, 2015, **7**, 14328–14337.
- 96 W. Wang, C. L. Bray, D. J. Adams and A. I. Cooper, *J. Am. Chem. Soc.*, 2008, **130**, 11608–11609.
- 97 Z. Zhao, C. Ling, D. Wang, J. Wang, J. Saczek, S. Pramana, S. Sridhar, J. Shang, B. B. Xu, D. C. W. Tsang, J. Chen and S. Wang, *Small*, 2020, **16**, 2002802.
- 98 H. Zhao, Y. Yang, Y. Chen, J. Li, L. Wang and C. Li, *Chem. Eng. Sci.*, 2022, **248**, 117085.
- 99 P. K. Roy, B. P. Binks, E. Bormashenko, I. Legchenkova, S. Fujii and S. Shoval, *J. Colloid Interface Sci.*, 2020, **575**, 35–41.
- 100 D. Quéré, *Rep. Prog. Phys.*, 2005, **68**, 2495–2532.
- 101 T.-S. Wong, S. H. Kang, S. K. Y. Tang, E. J. Smythe, B. D. Hatton, A. Grinthal and J. Aizenberg, *Nature*, 2011, **477**, 443–447.
- 102 A. Lafuma and D. Quéré, *Europhys. Lett.*, 2011, **96**, 56001.
- 103 M. Anyfantakis, V. S. R. Jampani, R. Kizhakidathazhath, B. P. Binks and J. P. F. Lagerwall, *Angew. Chem., Int. Ed.*, 2020, **59**, 19260–19267.



- 104 P. K. Roy, B. P. Binks, S. Shoval, L. A. Dombrovsky and E. Bormashenko, *J. Colloid Interface Sci.*, 2022, **626**, 466–474.
- 105 K. Aono, K. Ueno, S. Hamasaki, Y. Sakurai, S. Yusa, Y. Nakamura and S. Fujii, *Langmuir*, 2022, **38**, 7603–7610.
- 106 T. Takei, R. Tomimatsu, T. Matsumoto, K. R. Sreejith, N.-T. Nguyen and M. Yoshida, *Polymers*, 2022, **14**, 4849.
- 107 R. Murakami, S. Kobayashi, M. Okazaki, A. Bismarck and M. Yamamoto, *Front. Chem.*, 2018, **6**, 435.
- 108 R. W. Style, R. Boltianskiy, Y. Che, J. S. Wettlaufer, L. A. Wilen and E. R. Dufresne, *Phys. Rev. Lett.*, 2013, **110**, 066103.
- 109 B. Andreotti and J. H. Snoeijer, *Annu. Rev. Fluid Mech.*, 2020, **52**, 285–308.
- 110 M. Tenjimbayashi, S. Samitsu, Y. Watanabe, Y. Nakamura and M. Naito, *Adv. Funct. Mater.*, 2021, **31**, 2010957.
- 111 C. P. McLaren, T. M. Kovar, A. Penn, C. R. Müller and C. M. Boyce, *Proc. Natl. Acad. Sci. U. S. A.*, 2019, **116**, 9263–9268.
- 112 B. S. Lekshmi and S. N. Varanakkottu, *Droplet*, 2023, **2**, e44.
- 113 J. Fujiwara, A. Yokoyama, M. Seike, N. Vogel, M. Rey, K. Oyama, T. Hirai, Y. Nakamura and S. Fujii, *Mater. Adv.*, 2021, **2**, 4604–4609.
- 114 J. Niu, W. Liu, J. X. Li, X. Pang, Y. Liu, C. Zhang, K. Yue, Y. Zhou, F. Xu, X. Li and F. Li, *Nat. Commun.*, 2023, **14**, 3853.
- 115 C. Py, P. Reverdy, L. Doppler, J. Bico, B. Roman and C. N. Baroud, *Phys. Rev. Lett.*, 2007, **98**, 156103.
- 116 Y. Zhang, Z. Huang, Z. Cai, Y. Ye, Z. Li, F. Qin, J. Xiao, D. Zhang, Q. Guo, Y. Song and J. Yang, *Sci. Adv.*, 2021, **7**, eabi7498.
- 117 X. Li, Y. Xue, P. Lv, H. Lin, F. Du, Y. Hu, J. Shen and H. Duan, *Soft Matter*, 2016, **12**, 1655–1662.
- 118 X. Guo, N. Xue, M. Zhang, R. Ettelaie and H. Yang, *Nat. Commun.*, 2022, **13**, 5935.
- 119 Z. Wang, G. Zhu, Q. Wang, K. Ding, Y. Tong and C. Gao, *Sep. Purif. Technol.*, 2022, **301**, 122046.
- 120 S. Wooh, H. Huesmann, M. N. Tahir, M. Paven, K. Wichmann, D. Vollmer, W. Tremel, P. Papadopoulos and H.-J. Butt, *Adv. Mater.*, 2015, **27**, 7338–7343.
- 121 J. Heo, J. Lee, W. Shim, H. Kim, S. Fujii, J. Lim, M. Kappl, H.-J. Butt and S. Wooh, *ACS Appl. Mater. Interfaces*, 2023, **15**, 38986–38995.
- 122 H. Tan, S. Wooh, H.-J. Butt, X. Zhang and D. Lohse, *Nat. Commun.*, 2019, **10**, 478.
- 123 S. M. Salehabad and S. Azizian, *Colloids Surf., A*, 2021, **620**, 126551.
- 124 Y. Kim, S. Oh, H. Lee, D. Lee, M. Kim, H. S. Baek, W. S. Park, E. Kim and J.-H. Jang, *Biomater. Sci.*, 2021, **9**, 1639–1651.
- 125 S. M. Salehabad, S. Azizian and S. Fujii, *Langmuir*, 2019, **35**, 8950–8960.
- 126 V. Narayanamurthy, Z. E. Jeroish, K. S. Bhuvaneshwari, P. Bayat, R. Premkumar, F. Samsuri and M. M. Yusoff, *RSC Adv.*, 2020, **10**, 11652–11680.
- 127 D. T. Tran, A. S. Yadav, N.-K. Nguyen, P. Singha, C. H. Ooi and N.-T. Nguyen, *Small*, 2023, 2303435.
- 128 Z. Huang, Y. Xie, H. Chen, Z. Yu, L. Shi and J. Jin, *Processes*, 2023, **11**, 983.
- 129 N.-K. Nguyen, C. H. Ooi, P. Singha, J. Jin, K. R. Sreejith, H.-P. Phan and N.-T. Nguyen, *Processes*, 2020, **8**, 793.
- 130 E. Bormashenko, R. Balter and D. Aurbach, *Int. J. Chem. React. Eng.*, 2011, **9**, 1.
- 131 W. Wei, R. Lu, W. Ye, J. Sun, Y. Zhu, J. Luo and X. Liu, *Langmuir*, 2016, **32**, 1707–1715.
- 132 K. Lin, R. Chen, L. Zhang, D. Zang, X. Geng and W. Shen, *ACS Appl. Mater. Interfaces*, 2019, **11**, 8789–8796.
- 133 J. Tian, T. Arbatan, X. Li and W. Shen, *Chem. Commun.*, 2010, **46**, 4734.
- 134 A. Adamatzky, M. Tsompanas, T. C. Draper, C. Fullarton and R. Mayne, *ChemPhysChem*, 2020, **21**, 90–98.
- 135 N. El-Atab, R. B. Mishra, F. Al-Modaf, L. Joharji, A. A. Alsharif, H. Alamoudi, M. Diaz, N. Kaiser and M. M. Hussain, *Adv. Intell. Syst.*, 2020, **2**, 2000128.
- 136 C. H. Ooi, R. Vadivelu, J. Jin, K. R. Sreejith, P. Singha, N.-K. Nguyen and N.-T. Nguyen, *Lab Chip*, 2021, **21**, 1199–1216.
- 137 Y. Sun, Y. Zheng, C. Liu, Y. Zhang, S. Wen, L. Song and M. Zhao, *RSC Adv.*, 2022, **12**, 15296–15315.
- 138 N.-K. Nguyen, P. Singha, Y. Dai, K. R. Sreejith, D. T. Tran, H.-P. Phan, N.-T. Nguyen and C. H. Ooi, *Lab Chip*, 2022, **22**, 1508–1518.
- 139 X. Pang, M. Duan, H. Liu, Y. Xi, H. Shi and X. Li, *ACS Appl. Mater. Interfaces*, 2022, **14**, 11999–12009.
- 140 N. Barman, A. Shome, S. Kumar, P. Mondal, K. Jain, M. Tenjimbayashi and U. Manna, *Adv. Funct. Mater.*, 2023, **33**, 2214840.
- 141 T. C. Draper, N. Phillips, R. Weerasekera, R. Mayne, C. Fullarton, B. P. J. de Lacy Costello and A. Adamatzky, *Lab Chip*, 2020, **20**, 136–146.
- 142 J. C. Gomez, N. S. Vishnosky, S. T. Kim, S. A. Dinca, E. B. Finkelstein and R. C. Steinhardt, *Adv. Funct. Mater.*, 2023, **33**, 2214893.
- 143 S. X. Leong, L. K. Koh, C. S. L. Koh, G. C. Phan-Quang, H. K. Lee and X. Y. Ling, *ACS Appl. Mater. Interfaces*, 2020, **12**, 33421–33427.
- 144 H. Li, P. Liu, R. Gunawan, Z. M. Simeneh, C. Liang, X. Yao and M. Yang, *Adv. Healthcare Mater.*, 2021, **10**, 2001658.
- 145 J. Niu, H. Shi, H. Wei, B. Gao, J. X. Li, F. Xu, X. Li and F. Li, *Anal. Chem.*, 2020, **92**, 9048–9056.
- 146 M. Liu, C. Chen, J. Yu, H. Zhang, L. Liang, B. Guo, Y. Qiu, F. Yao, H. Zhang and J. Li, *Mater. Today Bio*, 2022, **17**, 100477.
- 147 A. Langella, S. D. Gadau, E. Serra, D. Bebbere and S. Ledda, *Biology*, 2022, **11**, 492.
- 148 R. Vadivelu, N. Kashaninejad, M. R. Nikmaneshi, R. R. Khadim, S. S. Salehi, N. C. Ramulu, Y. Sakai, M. Nishikawa, B. Firoozabadi and N. Nguyen, *Adv. Biol.*, 2021, **5**, 2000108.
- 149 W. Ramadhan, Y. Ohama, K. Minamihata, K. Moriyama, R. Wakabayashi, M. Goto and N. Kamiya, *J. Biosci. Bioeng.*, 2020, **130**, 416–423.



- 150 J. Aalders, L. Léger, T. Tuerlings, S. Ledda and J. van Hengel, *MethodsX*, 2020, **7**, 101065.
- 151 A. Walther, *Adv. Mater.*, 2020, **32**, 1905111.
- 152 T. Matsuda, R. Kawakami, R. Namba, T. Nakajima and J. P. Gong, *Science*, 2019, **363**, 504–508.
- 153 Y. Wang, L. Li, D. Hofmann, J. E. Andrade and C. Daraio, *Nature*, 2021, **596**, 238–243.
- 154 M. Tenjimayashi and M. Naito, *Adv. Funct. Mater.*, 2022, **32**, 2204681.
- 155 J. Zhang, B. Chen, X. Chen and X. Hou, *Adv. Mater.*, 2021, **33**, 2005664.

