

Cite this: *J. Mater. Chem. B*, 2023, 11, 3124

# Iron nitroprusside as a chemodynamic agent and inducer of ferroptosis for ovarian cancer therapy†

Kanwal Asif,<sup>ab</sup> Muhammad Adeel,<sup>\*ab</sup> Md. Mahbubur Rahman,<sup>id \*c</sup> Isabella Caligiuri,<sup>b</sup> Tiziana Perin,<sup>b</sup> Maja Cemazar,<sup>d</sup> Vincenzo Canzonieri<sup>id be</sup> and Flavio Rizzolio<sup>id \*ab</sup>

ChemoDynamic Therapy (CDT) is a powerful therapeutic modality using Fenton/Fenton-like reactions to produce oxidative stress for cancer treatment. However, the insufficient amount of catalyst ions and ROS scavenging activity of glutathione peroxidase (GPX4) limit the application of this approach. Therefore, a tailored strategy to regulate the Fenton reaction more efficiently (utilizing dual metal cations) and inhibit the GPX4 activity, is in great demand. Herein, a CDT system is based on dual (Fe<sup>2+</sup> metals) iron pentacyanonitrosylferrate or iron nitroprusside (FeNP) having efficient ability to catalyze the reaction of endogenous H<sub>2</sub>O<sub>2</sub> to form highly toxic •OH species in cells. Additionally, FeNP is involved in ferroptosis via GPX4 inhibition. In particular, FeNP was structurally characterized, and it is noted that a minimum dose of FeNP is required to kill cancer cells while a comparable dose shows negligible toxicity on normal cells. Detailed *in vitro* studies confirmed that FeNP participates in sustaining apoptosis, as determined using the annexin V marker. Cellular uptake results showed that in a short time period, FeNP enters lysosomes and, due to the acidic lysosomal pH, releases Fe<sup>2+</sup> ions, which are involved in ROS generation (•OH species). Western blot analyses confirmed the suppression of GPX4 activity over time. Importantly, FeNP has a therapeutic effect on ovarian cancer organoids derived from High-Grade Serous Ovarian Cancer (HGSOC). Furthermore, FeNP showed biocompatible nature towards normal mouse liver organoids and *in vivo*. This work presents the effective therapeutic application of FeNP as an efficient Fenton agent along with ferroptosis inducer activity to improve CDT, through disturbing redox homeostasis.

Received 10th December 2022,  
Accepted 9th February 2023

DOI: 10.1039/d2tb02691k

rsc.li/materials-b

## 1. Introduction

To cope with the continuing threat of cancer, ChemoDynamic Therapy (CDT) is considered one of the most promising cancer therapeutic approaches with minimal toxicity through a Fenton reaction.<sup>1</sup> In particular, besides iron, other metals including Cu, Mn, Co, Ti, V, Pd, and Ag act as CDT agents *via* Fenton/Fenton-like reactions.<sup>2–10</sup> CDT induces severe oxidative damage

*via* the catalysed conversion of hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) into a lethal hydroxyl radical (•OH), resulting in an increased intracellular oxidative stress and lipid oxidation, which lead to cell death.<sup>2,3,11–14</sup> It has been reported that CDT has low toxicity towards normal cells compared to the cancerous cells, because metals have poor catalytic activity above pH 4<sup>15</sup> while they are more effective towards tumor cells due to their low acidic tumor microenvironment compared to traditional chemotherapeutics.<sup>16–18</sup> However, there is no external stimulation required to initiate the Fenton reaction *via* CDT,<sup>11,19,20</sup> compared to other cancer therapeutic approaches.<sup>21</sup> Other than the Fenton reaction to produce reactive oxygen species (ROS),<sup>22–24</sup> iron-based materials promote ferroptosis-mediated cell death. Ferroptosis is an iron-dependent form of cell death, which is related to the intracellular iron concentration<sup>25,26</sup> and plays an important role in tumor growth suppression.<sup>27</sup> Ferroptosis requires the inactivation of glutathione peroxidase (GPX4) or glutathione (GSH) depletion in order to produce an abundant amount of ROS<sup>28–30</sup> to induce cell death.

<sup>a</sup> Department of Molecular Sciences and Nanosystems, Ca' Foscari University of Venice, 30172, Venice, Italy. E-mail: muhammad.adeel@unive.it, flavio.rizzolio@unive.it

<sup>b</sup> Pathology Unit, Centro di Riferimento Oncologico di Aviano (C.R.O.) IRCCS, 33081, Aviano, Italy

<sup>c</sup> Department of Applied Chemistry, Konkuk University, Chungju 27478, Republic of Korea. E-mail: mahbub1982@kku.ac.kr

<sup>d</sup> Department of Experimental Oncology, Institute of Oncology Ljubljana, Zaloska cesta 2, SI-1000 Ljubljana, Slovenia

<sup>e</sup> Department of Medical, Surgical and Health Sciences, University of Trieste, 34149, Trieste, Italy


† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2tb02691k>





### 2.3 Synthesis of FeNP

A simple solution mixing procedure was employed to synthesize FeNP. Briefly, 40 mL of 0.2 M FeCl<sub>2</sub> solution in methanol was mixed with 40 mL of 0.4 M SNP solution in methanol and stirred for 12 h at 70 °C. After the completion of the reaction, the reaction mixture was cooled to RT. Subsequently, the precipitates of FeNP were collected by centrifugation at 12 000 RPM for 30 min, washed several times with methanol, and dried at 40 °C overnight in a vacuum oven at 40 °C. The chemical reaction for the synthesis of FeNP can be written as follows:



### 2.4 Cell viability

For cell viability measurements, SK-OV-3, MDA-MB-231, A2780, A2780 cis, U-87 MG and MCF-7 cells were seeded in 96-well plates at densities of  $1 \times 10^3$  and, for MRC-5,  $8 \times 10^3$  per well and treated with six concentrations (0.001, 0.01, 0.1, 1, 10 and 100 µg) of iron nitroprusside (FeNP) and its precursors iron chloride (FeCl<sub>2</sub>) and sodium nitroprusside (SNP). As a positive control, we treated cells with six concentrations of CisPt starting from 30 µg ml<sup>-1</sup> (100 µM) to 0.001 µg ml<sup>-1</sup> (0.03 µM). After 96 hours, cell viability was measured using the CellTiter-Glo<sup>®</sup> assay system according to the manufacturer's instructions (Promega, Madison, WI, USA). Luminescence was recorded using a Tecan M1000 instrument. Experiments were performed in triplicate and IC<sub>50</sub> values were analysed using a non-linear regression method using GraphPad Prism software.

### 2.5 Stability of FeNP

The stability of FeNP was measured by developing an artificial *in vivo* system through mixing FeNP in physiological solutions with two different pH values (pH 5.5 and pH 7.4). Next, the solutions were kept in an incubator at 37 °C. Then samples were taken at different day intervals (0–7; D0, D1, D2, D3, D5, and D7), centrifuged, and collected. After that, samples were measured by UV-vis absorption spectroscopy by mixing them in DI water.

### 2.6 Intracellular localization

SK-OV-3 cells were plated at a density of  $2 \times 10^5$  cells per mL in 6 well plates containing a glass coverslip for 24 h to allow cell attachment. Afterward, 50 µg ml<sup>-1</sup> of FeNP labelled with 30 µg ml<sup>-1</sup> of rhodamine B was added for 6, 24 and 48 h. Cells were washed twice with PBS and then incubated with 200 nM LysoTracker<sup>™</sup>Green DND-26 (ThermoFisher Scientific, Waltham, MA, USA) for lysosomes and 200 ng ml<sup>-1</sup> Hoechst 33342 for nuclear staining, respectively. Next, to fix cells, 4% paraformaldehyde was used for 20 minutes and then the coverslip was mounted using FluorSave mounting media (Merck Millipore, Burlington, MA, USA) for cellular imaging. The cellular uptake of FeNP was observed under a fluorescence microscope with appropriate filters. Images were analysed using ImageJ and JacoP plugins.

### 2.7 Flow cytometry analysis

SK-OV-3 cells were cultured at a density of  $2 \times 10^5$  in 6 multi-well plates as suggested by the supplier for indicated time points.

Following treatment, cells were washed with PBS, then harvested and labelled with a PE-Annexin V Apoptosis Detection Kit from Becton-Dickinson, Franklin Lakes, NJ, USA for 15 min in darkness. After, samples were examined using a BD Canto II flow cytometer and BD FACS DIVA software.

### 2.8 H<sub>2</sub>O<sub>2</sub> level measurement

To quantify the H<sub>2</sub>O<sub>2</sub> level, SK-OV-3 and MRC-5 were plated in 96 multi-well plates at a density of  $1 \times 10^4$  per well and incubated at 37 °C for 24 h. Then, cells were treated with 50 µg ml<sup>-1</sup> of FeNP, FeCl<sub>2</sub>, SNP and cisplatin (CisPt) (3 µg ml<sup>-1</sup>; 10 µM) for different time points (6, 24 and 48 h). The intracellular ROS H<sub>2</sub>O<sub>2</sub> level was measured by ROS-Glo<sup>™</sup> H<sub>2</sub>O<sub>2</sub> luminescence assay (Promega, Madison, WI, USA) corresponding to the manufacturer's guidelines on a Tecan M1000 instrument.

### 2.9 Cytochrome c release

SK-OV-3 cells were grown on coverslips at a density of  $2 \times 10^5$  cells per mL followed by the treatment of FeNP (50 µg ml<sup>-1</sup>) and CisPt (3 µg ml<sup>-1</sup>; 10 µM) for 6, 24 and 48 h. After each time point, 4% paraformaldehyde was used to fix the cells (20 min, RT). Furthermore, cells were permeabilized with 0.3% Triton X-100/PBS (15 min, RT) and blocked with 8% BSA/PBS (1 h, RT). Next, cells were stained with a mouse monoclonal anti-cytochrome c (6H2-B4) antibody (1:100 dilution in 1% BSA/PBS, at 4 °C, overnight) purchased from Cell Signaling Technology, Catalog no: 12963; Danvers, MA, USA, followed by secondary antibody staining (1:1000 dilution, Alexa Fluor<sup>®</sup> 488 dye) for 2 h at room temperature. For nuclear visualization, cells were stained with 1 mg mL<sup>-1</sup> of DAPI (1:10 000 dilution in PBS, RT, 1 min). The cells were washed three times with PBS after all incubation steps. The coverslips were mounted on glass slides with the FluorSave<sup>™</sup> reagent (Catalog no: 345789; Millipore: Burlington, MA, USA) and images were acquired using a Leica DM5500B fluorescence microscope with an X-Cite 120 PC Q lamp and analysed with Image J software.

### 2.10 Western blot analysis

SK-OV-3 cells were treated with FeNP, FeCl<sub>2</sub>, SNP (10 µg ml<sup>-1</sup>) and CisPt (3 µg ml<sup>-1</sup>; 10 µM) for 6, 24, and 48 h, then harvested and lysed using a radioimmunoprecipitation assay buffer containing protease and phosphatase (sodium fluoride (NaF) and sodium orthovanadate (Na<sub>3</sub>VO<sub>4</sub>)) inhibitors *via* vigorous sonication on an ice bath and the protein concentration was determined using the Bradford protein assay. 20 µg of proteins was used for SDS-PAGE and transferred to a nitrocellulose membrane. After protein transfer, the membranes were blocked in 5% (wt/v) non-fat milk and incubated with primary antibodies overnight: GPX4 (Catalog no: ab125066, dilution 1:500, Abcam, Cambridge, UK) and Vinculin (Catalog no: sc7649, dilution 1:5000, Santacruz Biotechnology, Dallas, TX, USA), followed by incubation with secondary antibodies conjugated with horseradish peroxidase (goat anti-rabbit immunoglobulin G, Catalog no: 31462, ThermoFisher Scientific, Waltham, MA, USA, and mouse anti-goat immunoglobulin G, Catalog no: 31400, ThermoFisher Scientific, Waltham, MA, USA) with dilution 1:10000. The immunoblot signals were generated using a Liteablot







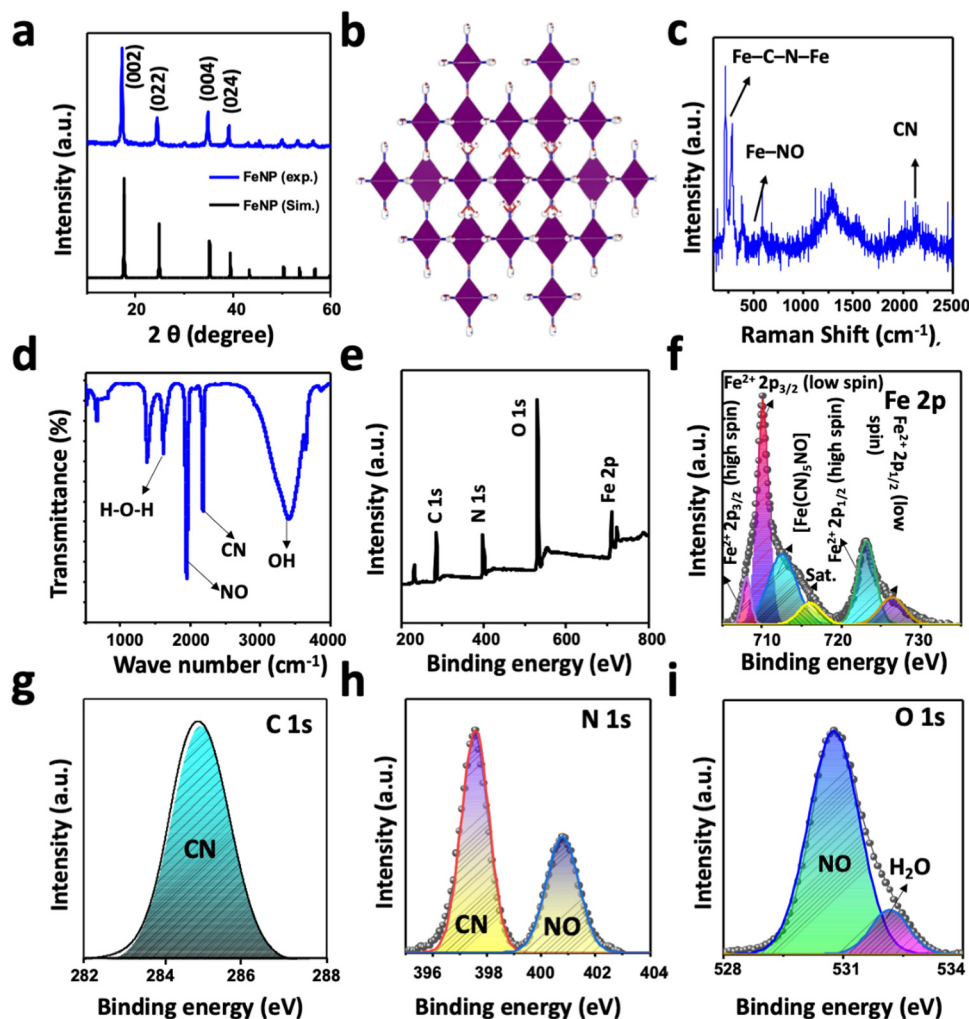


Fig. 1 (a) Powder XRD pattern of the as-prepared FeNP together with the simulated XRD pattern. (b) The crystal structure of FeNP. (c) Raman and (d) FTIR spectra of FeNP. (e) XPS survey spectra and high-resolution XPS spectra of (f) Fe 2p, (g) C 1s, (h) N 1s, and (i) O 1s. The line with the circle symbol and the shaded region represents the experimental and fitted data, respectively.

with XPS measurements. Fig. 1(e) displays the survey XPS spectra of FeNP, which exhibited the existence of C 1s, N 1s, O 1s, and Fe 2p peaks in their reported binding energy values.<sup>53</sup> The experimental high-resolution XPS spectra of Fe 2p, C 1s, N 1s, and O 1s are presented in Fig. 1(f)–(i), respectively, along with the fitted results. The high-resolution Fe 2p spectrum of FeNP showed spin–orbit doublet peaks of Fe 2p<sub>3/2</sub> and Fe 2p<sub>1/2</sub>. Both the peaks exhibited Fe<sup>2+</sup> low spin states at 710.0 and 726.0 eV, respectively, and Fe<sup>2+</sup> high spin states at 708.0 and 723.0 eV, respectively, originated from the Fe<sup>2+</sup> species.<sup>48,54</sup> The additional peak at 712.0 eV can be ascribed to the presence of [Fe(CN)<sub>5</sub>NO] in FeNP.<sup>49</sup> The appearance of these high-spin Fe<sup>2+</sup> peaks in FeNP can be attributed to the partial decomposition of FeNP induced by the high energy XPS beam that can be further confirmed by the presence of a satellite peak at 716.25 eV. The decomposition of FeNP induced by high energy XPS beam during measurement possibly altering of the Fe–CN bonds to Fe–NC bonds or breaking of the Fe–CN bond.<sup>48,54</sup> The deconvoluted core-level C 1s spectrum of FeNP showed only a CN

peak at 284.85 eV, while the high-resolution N 1s spectrum showed the CN and NO peaks at the binding energies of 397.58 and 400.80 eV, respectively. These binding energy values of chemical species of C 1s and N 1s spectra of FeNP are close to the reported results of other metal-nitroprussides.<sup>48,49,54</sup> The fitted O 1s spectra exhibited two-component peaks at 530.80 and 532.30 eV. The former peak can be assigned to the NO peak in FeNP, while the latter peak can be ascribed to the oxygen peak, originating from the adsorbed or crystalline water in FeNP.<sup>48</sup> The stability of FeNP was observed by establishing the artificial *in vivo* conditions in two different pHs (7.4 and 5.5) at 37 °C. After the treatment samples were taken at different time intervals and investigated by UV-vis absorption measurements (Fig. S1, ESI†). The results showed the presence of the FeNP absorption band at 270 nm without any visible shifting in the absorbance maxima at both pHs for up to 1 week, indicating the high stability of FeNP.

Fig. 2(a) and (b) show the FE-SEM images of FeNP under two-different magnifications. The surface morphology of the as-



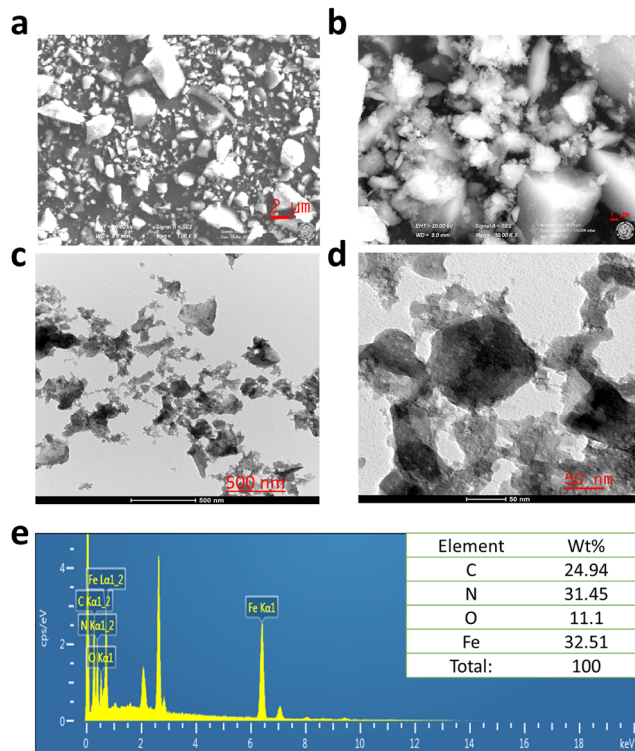


Fig. 2 (a) and (b) FE-SEM images, (c) and (d) HR-TEM images, and (e) EDS spectra of FeNP (inset table shows the elemental wt%).

synthesized FeNP exhibited the formation of mixed morphologies with a wide size distribution range. This was further confirmed with the HR-TEM images of the samples, which are presented in Fig. 2(c) and (d). The appearance of the smaller and larger particles in the sample can be further evidenced by the varying transparency of the electron beam in the HR-TEM images. To further confirm the characteristics of elements, present in FeNP, the EDS spectrum was measured, as shown in Fig. 2(e). The spectrum clearly revealed the presence of Fe, C, N, and O elemental peaks without the presence of other impurity peaks in the sample, and the corresponding elemental weight (%) was 32.51, 24.94, 31.45, and 11.10%, respectively.

### 3.2 FeNP induces cytotoxicity in cancer cells

To evaluate the cytotoxicity of FeNP, different cancerous cell lines (SK-OV-3, A2780, A2780cis, U87 MG, MDA-MB-231 and MCF-7) and a normal human fibroblast cell line (MRC-5) were treated with FeNP for 96 h. The potency of FeNP was shown mainly on ovarian cancer cell lines (SK-OV-3, A2780, and A2780cis) as well as other types of cancers including glioblastoma (U-87MG) and breast cancer (MDA-MB-231 and MCF-7). The cytotoxicity of the proposed FeNP is also significantly higher in the CisPt resistant ovarian cancer cell line (A2780cis) compared to the other treated groups (Fig. 3(c)).

Briefly, the  $IC_{50}$  values of FeNP and its precursor ( $FeCl_2$ ) against cancer cell lines are in the range of  $0.05$ – $3.16 \mu g ml^{-1}$  and  $0.09$ – $76.3 \mu g ml^{-1}$ , respectively. In comparison with CisPt

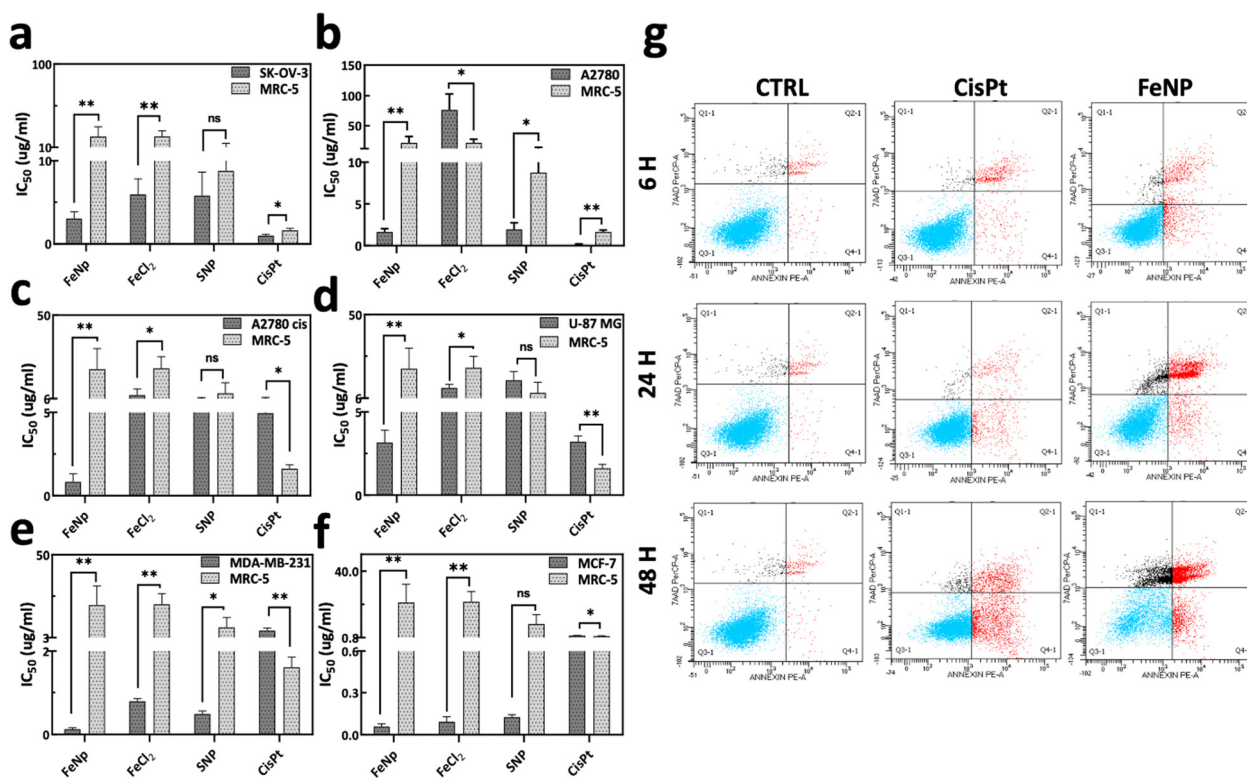


Fig. 3 Cytotoxic evaluation. (a)–(f)  $IC_{50}$  values of FeNP toward normal and cancer cells. Values are expressed in  $\mu g ml^{-1}$ . Data represent mean  $\pm$  SD ( $n = 3$ ). (g) Apoptosis analysis. The SK-OV-3 cells were analyzed by FACS using Annexin V/7AAD double staining after treatment of FeNP ( $50 \mu g ml^{-1}$ ) and CisPt ( $3 \mu g ml^{-1}$ ;  $10 \mu M$ ) for 6, 24 and 48 h (Q3: viable cells, Q4: early apoptosis, Q2: late apoptosis, and Q1: necrosis).



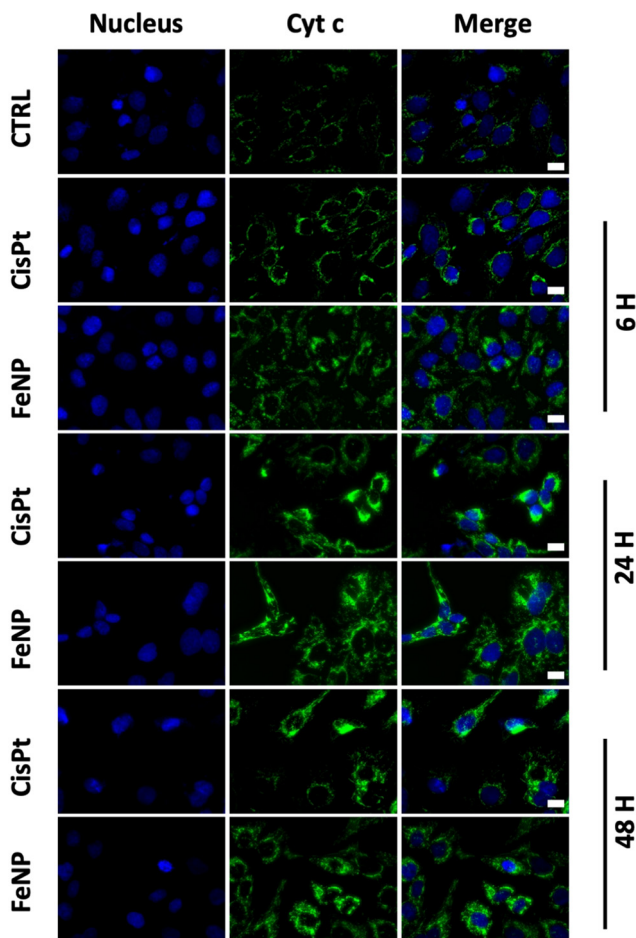


Fig. 4 Immunofluorescence analysis of cytochrome *c* release of SK-OV-3 cells incubated with FeNP ( $50 \mu\text{g ml}^{-1}$ ) and CisPt ( $3 \mu\text{g ml}^{-1}$ ;  $10 \mu\text{M}$ ) for 6, 24 and 48 h. Bar,  $10 \mu\text{m}$ .

on cancer cells, FeNP is more effective up to 54 fold. However, as depicted in Fig. 3(a)–(f), FeNP caused low or negligible toxicity to normal cells (0.07-fold). These data demonstrate that FeNP could release  $\text{Fe}^+$  ions inside the cells, which induce ROS species production and exert their toxicity. Complete data of  $\text{IC}_{50}$  values are listed in Table S1, ESI†. Hence, our results suggest that FeNP exhibits considerable toxicity towards all cancer cell lines while having less toxicity towards normal cells.

To validate the cell death mechanism caused by FeNP, annexin V/7AAD staining was performed following the treatment with FeNP,  $\text{FeCl}_2$  ( $10 \mu\text{g ml}^{-1}$ ) and CisPt ( $6 \mu\text{g ml}^{-1}$ ;  $20 \mu\text{M}$ ) of the SK-OV-3 cell line for 6, 24, and 48 h. Our data showed that the FeNP treatment leads to apoptosis, which increased over time as shown in Fig. 3(g) and Fig. S2c (ESI†). We observed a percentage of viable cells similar to control cells (92%) after 6 h of treatment which reduced to 71.3% and 29.0% after 24 h and 48 h of FeNP treatment. Additionally, there is an increase in early apoptosis from 1.2% in the control cells to 2.7%, 4.2% and 13.3% after 6, 24 and 48 h of FeNP treatment. A significant increase in the proportion of late apoptosis was observed, from 2.2% in control samples to 2.7%, 15.7% and 44.0% after 6, 24 and 48 h of FeNP treatment, respectively. Comparatively, apoptosis in precursors

and the CisPt group is lower than that due to FeNP (Fig. S2(a) and (b), ESI†). These results suggested that FeNP induces cell death *via* the apoptotic pathway.

### 3.3 Cytochrome *c* release

The release of cytochrome *c* is the major event during apoptosis.<sup>55,56</sup> For this reason, next we examine the release of cytochrome *c* into the cytosol from mitochondria. Based on the  $\text{IC}_{50}$  data, we incubated SK-OV-3 cells with FeNP,  $\text{FeCl}_2$ , SNP ( $50 \mu\text{g ml}^{-1}$ ) and CisPt ( $3 \mu\text{g ml}^{-1}$ ;  $10 \mu\text{M}$ ) for 6, 24, and 48 h and then compared them with untreated cells. As illustrated in Fig. 4 and Fig. S3 (ESI†) there is an obvious release of cyt *c* after 24 h of FeNP treatment compared to cisplatin and  $\text{FeCl}_2$ -treated cells. Our data suggest that there is a cyt *c* release in the cytosol leading to cell death.

### 3.4 Cellular uptake analysis

One of the challenges in cancer therapy is the lysosomal degradation of chemotherapeutic agents.<sup>57</sup> Colocalization experiments were performed to investigate the amount of FeNP internalized in lysosomes. To evaluate the FeNP accumulation, we incubated the SK-OV-3 cells for 6, 24 and 48 h at  $37^\circ\text{C}$  with FeNP labelled with rhodamine (red), the nucleus with Hoechst 33342 (blue) and lysosomes with Lysotracker™Green DND-26 (green). Fig. 5 shows the internalization of FeNP at each time point. The colocalization of FeNP and lysosomes was evaluated with Pearson's correlation coefficient (*R*) after each time point. Interestingly, "*R*" values after 6 and 24 h of treatment were 0.64 and 0.709 but after 48 h the values decreased to 0.59 for FeNP. These results suggest that FeNP initially goes partially inside the lysosomes in agreement with previous studies for iron nanoparticles<sup>58–60</sup> demonstrating the endocytotic uptake mechanism of FeNP, but with time, FeNP escapes lysosomal degradation and relocated to the cytoplasm.

We next examined the cell death mechanism through oxidative stress *via* ROS production. SK-OV-3 and MRC-5 cell lines were incubated with FeNP ( $50 \mu\text{g ml}^{-1}$ ) and CisPt ( $3 \mu\text{g ml}^{-1}$ ,  $10 \mu\text{M}$ ) for 6, 24 and 48 h. As shown in Fig. 6(a), in SK-OV-3 cells the  $\text{H}_2\text{O}_2$  levels increase after 48 h. This effect could be due to the reduction of the glutathione peroxidase 4 (GPX4) activity. Comparatively, in fibroblasts, the overall  $\text{H}_2\text{O}_2$  levels are higher than in SK-OV-3 as shown in Fig. 6(b) but are reduced with time due to the antioxidant activity. In comparison, between cancerous and normal cells, the overall  $\text{H}_2\text{O}_2$  levels are lower in cancerous cells because of the FeNP catalytic activity for efficient  $\bullet\text{OH}$  generation as a Fenton agent for subsequent damage of cancer cells.<sup>61,62</sup> Our results are in accordance with previous reports, which demonstrate that  $\bullet\text{OH}$  radical production depends on  $\text{H}_2\text{O}_2$  and the catalytic activity of iron nanoparticles for efficient  $\bullet\text{OH}$  generation to destroy cancer cells.<sup>61</sup>

Recently, it has been reported that iron nanoparticles induce cell death *via* a lysosomal degradation pathway due to an acidic lysosomal environment, which releases iron ions involved in the production of ROS leading to ferroptosis cell death.<sup>63,64</sup> There are a number of studies that demonstrated the role of ROS species in the ferroptotic cell death mechanism.<sup>65,66</sup>





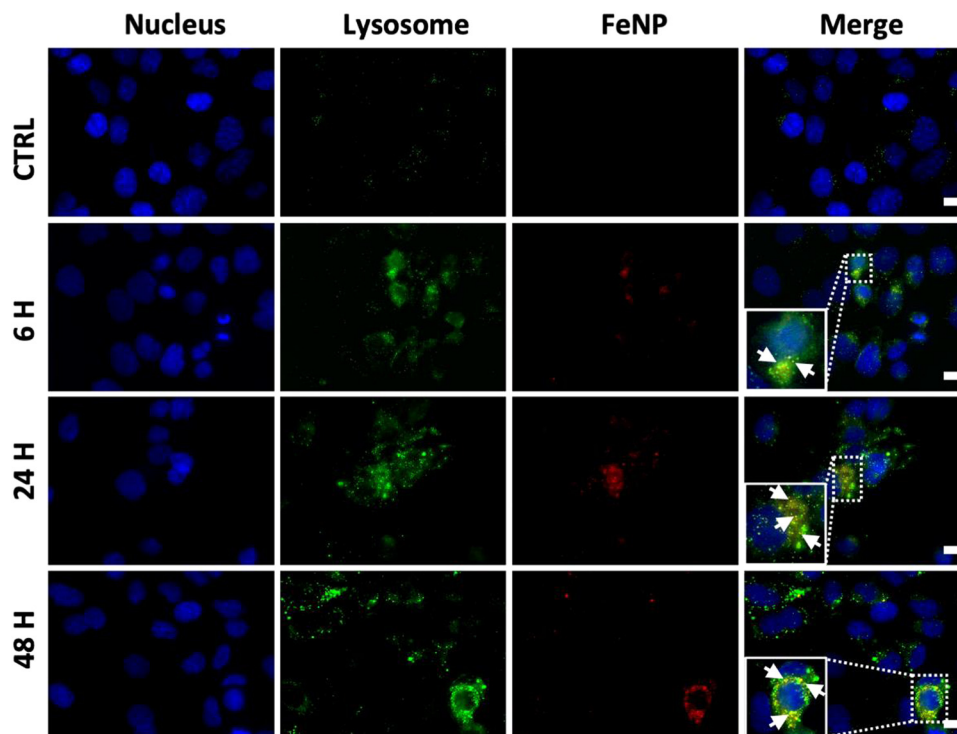


Fig. 5 Lysotracker analysis of an FeNP for the cell internalization study. Fluorescence microscopy images of a rhodamine-labeled FeNP of SK-OV-3 ovarian cancer cell line after 6, 24 and 48 h, from the left to the right, respectively. Negative control (only nuclei and lysosome staining, rhodamine) was used to set up the fluorescence intensity and avoid the background signal. Bar, 10  $\mu\text{m}$ . Cells were incubated with FeNP ( $50 \mu\text{g ml}^{-1}$ ) for 6, 24 and 48 h.

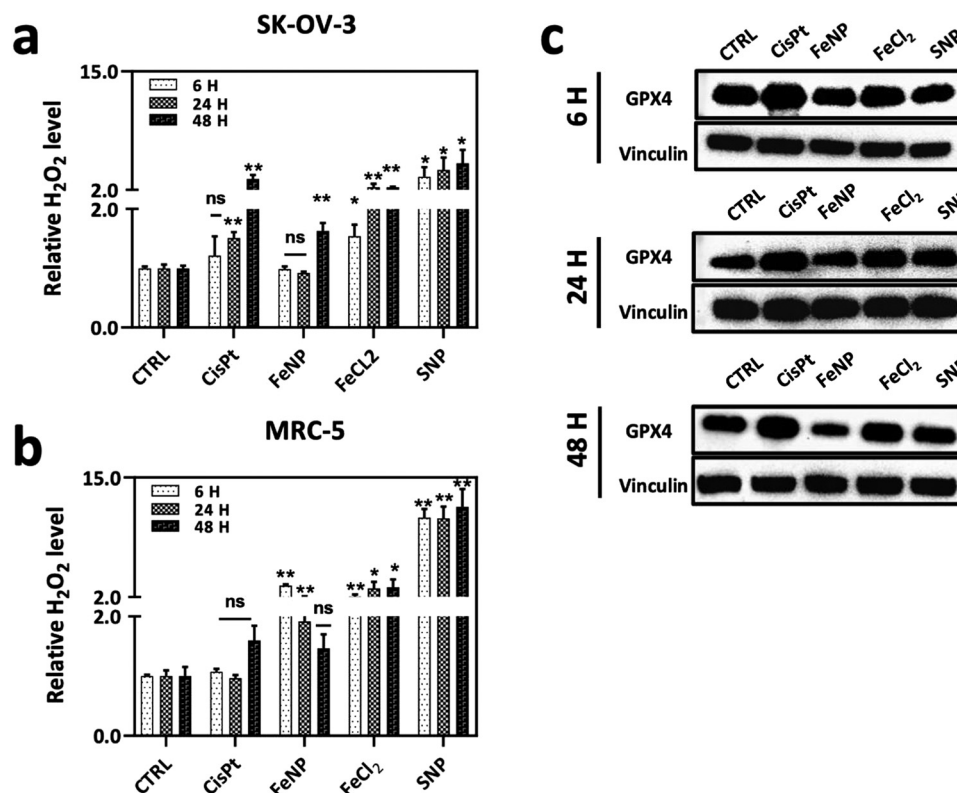


Fig. 6 (a) and (b) Relative H<sub>2</sub>O<sub>2</sub> level. (a) SK-OV-3 and (b) MRC-5 incubated with FeNP, FeCl<sub>2</sub>, SNP ( $50 \mu\text{g ml}^{-1}$ ) and CisPt ( $3 \mu\text{g ml}^{-1}$ ;  $10 \mu\text{M}$ ) for 6, 24 and 48 h. (c) Effect of FeNP on the GPX4 activity on the SK-OV-3 cell line, assessed by western blot after 6, 24 and 48 h of treatment. Cells were incubated with FeNP ( $50 \mu\text{g ml}^{-1}$ ) and CisPt ( $3 \mu\text{g ml}^{-1}$ ;  $10 \mu\text{M}$ ). Error bars indicate the SEM, and data shown are for two independent experiments of three replicates. Groups were considered statistically significant if  $p < 0.05$  (\*),  $p < 0.01$  (\*\*) and non-significant (ns).







Fig. 7 Cytotoxicity of FeNP and CisPt (a) in normal mouse liver organoids. (b)–(d) PDTO obtained from a HGSOc patient. Error bars indicate the SEM.



Fig. 8 Body weight change of tumor-bearing mice after treatment with FeNP and CisPt. Error bars indicate the SEM.

Ferroptosis is an iron-dependent programmed cell death, which is characterized by higher intracellular iron ions and ROS production.<sup>67</sup> Ferroptosis is activated by the depletion of the GPX4 activity. GPX4 is an antioxidant enzyme involved in repairing oxidative damage to lipids and acts as an inhibitor of ferroptosis. Thus, GPX4 is an important regulator of ferroptosis.<sup>68–70</sup> Therefore, next we determined the GPX4-mediated ferroptosis after FeNP treatment. As shown in Fig. 6(c), the GpX4 activity is similar after 6 and 24 h of treatment, but eventually, after 48 h the GPX4 activity is downregulated in SK-OV-3, which demonstrates the involvement of FeNP in the ferroptosis-mediated cell death pathway with apoptosis. Previously, it has been reported that

the reduced glutathione peroxidase activity leads to increased  $H_2O_2$  levels ultimately leading to  $\bullet OH$  production.<sup>71</sup> CisPt treatment showed upregulation of the GPX4 activity, which indicates a CisPt resistance mechanism *via* ferroptosis inhibition.<sup>72</sup> These data suggest that FeNP is involved in ROS production *via* a ferroptosis cell death mediated pathway.

### 3.5 Anticancer activity of FeNP on human ovarian cancer organoids

Normal mouse liver organoids were used to evaluate the toxicity effect of FeNP.<sup>73</sup> The  $IC_{50}$  value of FeNP ( $> 200 \mu g ml^{-1}$ ) was 21-fold higher than that of CisPt ( $9.2 \pm 1.9 \mu g ml^{-1}$ ). This suggests the biocompatibility of FeNP towards liver organoids compared to its precursors and CisPt (Fig. 7(a) and Table S2, ESI<sup>†</sup>).

Afterward, we examined the toxicity of FeNP on HGSOc patient-derived tumor organoids (PDTO), the most common type of ovarian cancer with the worst survival rate.<sup>74,75</sup> Patient-derived tumor organoids represent a useful *ex vivo* model to evaluate the therapeutic drug efficacy<sup>45,76,77</sup> as they mimic the patients' response in the clinic<sup>78</sup> compared to xenografts.<sup>79</sup> To better mimic the treatment option, we generated organoids from HGSOc patients to determine the efficacy of FeNP. In ovarian cancer, organoids could predict drug response in human patients.<sup>78,79</sup> As shown in Fig. 7(b)–(d) the  $IC_{50}$  values are in the range of  $0.3$ – $2.7 \mu g ml^{-1}$  (Table S2, ESI<sup>†</sup>).

To investigate the molecular similarity of organoids with the parental tumor, immunohistochemistry analysis was performed. We observed immunopositivity for CA125 (cancer antigen 125),



WT1 (Wilms Tumor 1) and PAX8 (paired box gene 8) which are markers of ovarian carcinoma (Fig, S4, ESI†).

### 3.6 *In vivo* biocompatibility of FeNP

Since FeNP was less toxic towards normal liver organoids, the biocompatibility of FeNP was investigated in mice. The mice were treated intraperitoneally twice per week with 2 mg kg<sup>-1</sup> of CisPt and up to 8 mg kg<sup>-1</sup> of FeNP. After treatment, mice were examined on a daily basis for signs of toxicity (physical distresses). As shown in Fig. 8, after FeNP treatment (8 mg kg<sup>-1</sup>) no obvious body weight changes are observed. These results demonstrate the biocompatible nature of FeNP.

## 4. Conclusion

In summary, we demonstrated a iron-based self-therapeutic nanosystem with dual ROS generation through the Fenton reaction for cancer therapy. Our results showed that FeNP decomposed H<sub>2</sub>O<sub>2</sub> via the Fenton reaction to produce more hydroxyl radical species in cancer cells due to the lysosomal acidic environment, thereby inducing more cancer cell destruction than in normal cells as demonstrated by flow cytometric analysis and the cytochrome *c* release test, which showed an increase in apoptosis over time. Furthermore, cell internalization analysis indicated that FeNP escapes the lysosomal degradation pathway and is localized in the cytoplasm. While at 6 and 24 h, FeNP decomposed more intracellular H<sub>2</sub>O<sub>2</sub> for hydroxyl radical species production, after 48 h there is an increase in the H<sub>2</sub>O<sub>2</sub> level due to the downregulation of the glutathione peroxidase gene (GPX4) demonstrating a ferroptosis mediated cell death mechanism. Furthermore, a low toxicity towards normal liver organoids and a high therapeutic efficacy towards cancer organoids indicate the potential of FeNP for future therapeutic applications.

## Author contributions

M. A. and K. A.: conceptualization, experimental data, and writing; M.d MR and I.C.: data analysis, review & editing, and writing; M. C.: animal data; T. P. and V. C.: biological samples, review & editing, and funding acquisition; F.R.: conceptualization, data analysis, and review & editing.

## Funding

This research was funded by the Ministry of Health, Ricerca Corrente.

## Conflicts of interest

The authors declare no conflict of interest.

## References

- C. Jia, Y. Guo and F. G. Wu, *Small*, 2022, **18**, 2103868.
- Z. Tang, Y. Liu, M. He and W. Bu, *Angew. Chem., Int. Ed.*, 2019, **58**, 946–956.
- Z. Tang, P. Zhao, H. Wang, Y. Liu and W. Bu, *Chem. Rev.*, 2021, **121**, 1981–2019.
- L. H. Fu, Y. Wan, C. Qi, J. He, C. Li, C. Yang, H. Xu, J. Lin and P. Huang, *Adv. Mater.*, 2021, **33**, 2006892.
- S. Jin, L. Weng, Z. Li, Z. Yang, L. Zhu, J. Shi, W. Tang, W. Ma, H. Zong and W. Jiang, *J. Mater. Chem. B*, 2020, **8**, 4620–4626.
- Y. Su, X. Zhang, G. Ren, Z. Zhang, Y. Liang, S. Wu and J. Shen, *Chem. Eng. J.*, 2020, **400**, 125949.
- G. Liu, J. Zhu, H. Guo, A. Sun, P. Chen, L. Xi, W. Huang, X. Song and X. Dong, *Angew. Chem., Int. Ed.*, 2019, **58**, 18641–18646.
- W. L. Wang, Z. Guo, Y. Lu, X. C. Shen, T. Chen, R. T. Huang, B. Zhou, C. Wen, H. Liang and B. P. Jiang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 17294–17305.
- P. Liu, Y. Wang, L. An, Q. Tian, J. Lin and S. Yang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 38833–38844.
- K. Xu, Y. Cheng, J. Yan, Y. Feng, R. Zheng, X. Wu, Y. Wang, P. Song and H. Zhang, *Nano Res.*, 2019, **12**, 2947–2953.
- S. L. Li, P. Jiang, F. L. Jiang and Y. Liu, *Adv. Funct. Mater.*, 2021, **31**, 2100243.
- X. Chen, Y. Liu and W. Bu, *Sci. Sin.: Chim.*, 2020, **50**, 159–172.
- Q. Tian, F. Xue, Y. Wang, Y. Cheng, L. An, S. Yang, X. Chen and G. Huang, *Nano Today*, 2021, **39**, 101162.
- K. Ni, T. Luo, G. T. Nash and W. Lin, *Acc. Chem. Res.*, 2020, **53**, 1739–1748.
- D. Wu, Y. Chen, Z. Zhang, Y. Feng, Y. Liu, J. Fan and Y. Zhang, *Chem. Eng. J.*, 2016, **294**, 49–57.
- J. Dinić, T. Efferth, A. T. García-Sosa, J. Grahovac, J. M. Padrón, I. Pajeva, F. Rizzolio, S. Saponara, G. Spengler and I. Tsakovska, *Drug Resist. Updates*, 2020, **52**, 100713.
- T. Scattolin, I. Caligiuri, L. Canovese, N. Demitri, R. Gambari, I. Lampronti, F. Rizzolio, C. Santo and F. Visentin, *Dalton Trans.*, 2018, **47**, 13616–13630.
- M. Aghazadeh Tabrizi, P. G. Baraldi, S. Baraldi, E. Ruggiero, L. De Stefano, F. Rizzolio, L. Di Cesare Mannelli, C. Ghelardini, A. Chicca, M. Lapillo, J. Gertsch, C. Manera, M. Macchia, A. Martinelli, C. Granchi, F. Minutolo and T. Tuccinardi, *J. Med. Chem.*, 2018, **61**, 1340–1354.
- X. Liu, Y. Jin, T. Liu, S. Yang, M. Zhou, W. Wang and H. Yu, *ACS Biomater. Sci. Eng.*, 2020, **6**, 4834–4845.
- R. Cao, W. Sun, Z. Zhang, X. Li, J. Du, J. Fan and X. Peng, *Chin. Chem. Lett.*, 2020, **31**, 3127–3130.
- P. Liu, Y. Peng, J. Ding and W. Zhou, *Asian J. Pharm. Sci.*, 2022, **17**, 177–192.
- J. Liu, R. Kang and D. Tang, *FEBS J.*, 2021, **289**, 7038–7050.
- D. Vitalakumar, A. Sharma and S. J. S. Flora, *J. Biochem. Mol. Toxicol.*, 2021, **35**, e22830.
- B. Xie and Y. Guo, *Cell Death Discovery*, 2021, **7**, 1–10.
- L. M. Bystrom, M. L. Guzman and S. Rivella, *Antioxid. Redox Signaling*, 2014, **20**, 1917–1924.
- S. Doll and M. Conrad, *IUBMB Life*, 2017, **69**, 423–434.
- Z. Xu, B. Peng, Q. Liang, X. Chen, Y. Cai, S. Zeng, K. Gao, X. Wang, Q. Yi, Z. Gong and Y. Yan, *Front. Immunol.*, 2021, **12**, 3728.



- 28 Y. Xie, W. Hou, X. Song, Y. Yu, J. Huang, X. Sun, R. Kang and D. Tang, *Cell Death Differ.*, 2016, **23**, 369–379.
- 29 A. Banjac, T. Perisic, H. Sato, A. Seiler, S. Bannai, N. Weiss, P. Kölle, K. Tschöep, R. D. Issels, P. T. Daniel, M. Conrad and G. W. Bornkamm, *Oncogene*, 2007, **27**, 1618–1628.
- 30 S. J. Dixon, D. Patel, M. Welsch, R. Skouta, E. Lee, M. Hayano, A. G. Thomas, C. Gleason, N. Tatonetti, B. S. Slusher and B. R. Stockwell, *eLife*, 2014, **3**, e02523.
- 31 L. Ying Guo, Q. Sheng Xia, J. Lei Qin, M. Yang, T. Yu Yang, F. Tian You, Z. Hua Chen, B. Liu and H. Shang Peng, *J. Colloid Interface Sci.*, 2022, **616**, 81–92.
- 32 X. Wang, P. Hua, C. He and M. Chen, *Acta Pharm. Sin. B*, 2022, **12**, 3567–3593.
- 33 Z. Shi, J. Zheng, W. Tang, Y. Bai, L. Zhang, Z. Xuan, H. Sun and C. Shao, *Front. Chem.*, 2022, **10**, 269.
- 34 L. Zhao, X. Zhou, F. Xie, L. Zhang, H. Yan, J. Huang, C. Zhang, F. Zhou, J. Chen and L. Zhang, *Cancer Commun.*, 2022, **42**, 88–116.
- 35 M. Zhang, X. Qin, Z. Zhao, Q. Du, Q. Li, Y. Jiang and Y. Luan, *Nanoscale Horiz.*, 2022, **7**, 198–210.
- 36 F. Zhao, J. Yao, Y. Tong, D. Su, Q. Xu, Y. Ying, W. Li, J. Li, J. Zheng, L. Qiao, W. Cai, X. Mou, S. Che, J. Yu and Y. Hou, *Mater. Adv.*, 2022, **3**, 1191–1199.
- 37 X. Wang, X. Zhong, Z. Liu and L. Cheng, *Nano Today*, 2020, **35**, 100946.
- 38 L. Chen, Z. Lin, L. Liu, X. Zhang, W. Shi, D. Ge and Y. Sun, *ACS Biomater. Sci. Eng.*, 2019, **5**, 4861–4869.
- 39 Z. Li, X. Wu, W. Wang, C. Gai, W. Zhang, W. Li and D. Ding, *Nanoscale Res. Lett.*, 2021, **16**, 1–11.
- 40 Z. Dong, L. Feng, Y. Chao, Y. Hao, M. Chen, F. Gong, X. Han, R. Zhang, L. Cheng and Z. Liu, *Nano Lett.*, 2019, **19**, 805–815.
- 41 X. Liu, X. Zhu, X. Qi, X. Meng and K. Xu, *Int. J. Nanomed.*, 2021, **16**, 1037–1050.
- 42 X. Wang, X. Zhong, H. Lei, Y. Geng, Q. Zhao, F. Gong, Z. Yang, Z. Dong, Z. Liu and L. Cheng, *Chem. Mater.*, 2019, **31**, 6174–6186.
- 43 B. Ma, S. Wang, F. Liu, S. Zhang, J. Duan, Z. Li, Y. Kong, Y. Sang, H. Liu, W. Bu and L. Li, *J. Am. Chem. Soc.*, 2019, **141**, 849–857.
- 44 H. Miyoshi and T. S. Stappenbeck, *Nat. Protoc.*, 2013, **8**, 2471–2482.
- 45 T. Scattolin, E. Bortolamiol, F. Visentin, S. Palazzolo, I. Caligiuri, T. Perin, V. Canzonieri, N. Demitri, F. Rizzolio and A. Togni, *Chem. – Eur. J.*, 2020, **26**, 11868–11876.
- 46 N. K. Chaturvedi, M. J. Kling, D. W. Coulter, T. R. McGuire, S. Ray, V. Keshnerwani, S. S. Joshi and J. G. Sharp, *Oncotarget*, 2018, **9**, 16619–16633.
- 47 E. I. Hassanen, R. M. S. Korany and A. M. Bakeer, *J. Biochem. Mol. Toxicol.*, 2021, **35**, e22722.
- 48 M. M. Rahman, *Materials*, 2021, **14**, 6563.
- 49 L. Reguera, Y. Avila and E. Reguera, *Coord. Chem. Rev.*, 2021, **434**, 213764.
- 50 A. Djebli, A. Boudjemaa, H. Bendjeffal, H. Mamine, T. Metidji, H. Bekakria and Y. Bouhedja, *Materials*, 2020, **50**, 1115–1122.
- 51 M. E. Chacón Villalba, E. L. Varetti and P. J. Aymonino, *Vib. Spectrosc.*, 2000, **23**, 31–38.
- 52 H. Razmi and H. Heidari, *Anal. Biochem.*, 2009, **388**, 15–22.
- 53 A. Mullaliu, G. Aquilanti, J. R. Plaisier, M. Giorgetti, B. Barbiellini, J. Kuriplach and R. Saniz, *Condens. Matter*, 2021, **6**, 27.
- 54 A. Cano, J. Rodríguez-Hernández, A. Shchukarev and E. Reguera, *J. Solid State Chem.*, 2019, **273**, 1–10.
- 55 D. R. Green and J. C. Reed, *Science*, 1998, **31**, 118.
- 56 A. Matapurkar and Y. Lazebnik, *Cell Death Differ.*, 2006, **13**, 2062–2067.
- 57 J. Hraběta, M. Belhajová, H. Šubrtová, M. A. M. Rodrigo, Z. Heger and T. Eckschlager, *Int. J. Mol. Sci.*, 2020, **21**, 1–18.
- 58 O. Lunov, T. Syrovets, B. Büchele, X. Jiang, C. Röcker, K. Tron, G. U. Nienhaus, P. Walther, V. Mailänder, K. Landfester and T. Simmet, *Biomaterials*, 2010, **31**, 5063–5071.
- 59 N. Kohler, C. Sun, J. Wang and M. Zhang, *Langmuir*, 2005, **21**, 8858–8864.
- 60 C. Wilhelm and F. Gazeau, *Biomaterials*, 2008, **29**, 3161–3174.
- 61 C. Zhang, W. Bu, D. Ni, S. Zhang, Q. Li, Z. Yao, J. Zhang, H. Yao, Z. Wang and J. Shi, *Angew. Chem., Int. Ed.*, 2016, **55**, 2101–2106.
- 62 H. Ranji-Burachaloo, P. A. Gurr, D. E. Dunstan and G. G. Qiao, *ACS Nano*, 2018, **12**, 11819–11837.
- 63 S. Wang, J. Luo, Z. Zhang, D. Dong, Y. Shen, Y. Fang, L. Hu, M. Liu, C. Dai, S. Peng, Z. Fang and P. Shang, *Am. J. Cancer Res.*, 2018, **8**, 1933.
- 64 A. Viktorinova, *Arch. Biochem. Biophys.*, 2018, **654**, 185–193.
- 65 M. Gao, P. Monian, Q. Pan, W. Zhang, J. Xiang and X. Jiang, *Cell Res.*, 2016, **26**, 1021–1032.
- 66 L. Jiang, N. Kon, T. Li, S. J. Wang, T. Su, H. Hibshoosh, R. Baer and W. Gu, *Nature*, 2015, **520**, 57–62.
- 67 A. Weiland, Y. Wang, W. Wu, X. Lan, X. Han, Q. Li and J. Wang, *Mol. Neurobiol.*, 2019, **56**, 4880–4893.
- 68 X. Song, X. Wang, Z. Liu and Z. Yu, *Front. Oncol.*, 2020, **10**, 597434.
- 69 T. M. Seibt, B. Proneth and M. Conrad, *Free Radical Biol. Med.*, 2019, **133**, 144–152.
- 70 A. Seiler, M. Schneider, H. Förster, S. Roth, E. K. Wirth, C. Culmsee, N. Plesnila, E. Kremmer, O. Rådmark, W. Wurst, G. W. Bornkamm, U. Schweizer and M. Conrad, *Cell Metab.*, 2008, **8**, 237–248.
- 71 J. Čapek and T. Roušar, *Molecules*, 2021, **26**, 4710.
- 72 X. Zhang, G. Gu, X. Li and C. Zhang, *Cell Cycle*, 2020, **19**, 2530–2537, DOI: [10.1080/15384101.2020.1809914](https://doi.org/10.1080/15384101.2020.1809914).
- 73 S. Palazzolo, M. Hadla, C. R. Spena, I. Caligiuri, R. Rotondo, M. Adeel, V. Kumar, G. Corona, V. Canzonieri, G. Toffoli and F. Rizzolio, *Cancers*, 2019, **11**, 1997.
- 74 D. D. Bowtell, S. Böhm, A. A. Ahmed, P. J. Aspuria, R. C. Bast, V. Beral, J. S. Berek, M. J. Birrer, S. Blagden, M. A. Bookman, J. D. Brenton, K. B. Chiappinelli, F. C. Martins, G. Coukos, R. Drapkin, R. Edmondson, C. Fotopoulou, H. Gabra, J. Galon, C. Gourley, V. Heong, D. G. Huntsman, M. Iwanicki, B. Y. Karlan, A. Kaye, E. Lengyel, D. A. Levine, K. H. Lu, I. A. McNeish, U. Menon, S. A. Narod, B. H. Nelson, K. P. Nephew, P. Pharoah, D. J. Powell, P. Ramos, I. L. Romero,





- C. L. Scott, A. K. Sood, E. A. Stronach and F. R. Balkwill, *Nat. Rev. Cancer*, 2015, **15**, 668–679.
- 75 M. Govindarajan, C. Wohlmuth, M. Waas, M. Q. Bernardini and T. Kislinger, *J. Hematol. Oncol.*, 2020, **13**, 1–20.
- 76 T. Scattolin, I. Pessotto, E. Cavarzerani, V. Canzonieri, L. Orian, N. Demitri, C. Schmidt, A. Casini, E. Bortolamiol, F. Visentin, F. Rizzolio and S. P. Nolan, *Eur. J. Inorg. Chem.*, 2022, e202200103.
- 77 J. Kim, B. K. Koo and J. A. Knoblich, *Nat. Rev. Mol. Cell Biol.*, 2020, **21**, 571–584.
- 78 S. J. Hill, B. Decker, E. A. Roberts, N. S. Horowitz, M. G. Muto, M. J. Worley, C. M. Feltmate, M. R. Nucci, E. M. Swisher, H. Nguyen, C. Yang, R. Morizane, B. S. Kochupurakkal, K. T. Do, P. A. Konstantinopoulos, J. F. Liu, J. V. Bonventre, U. A. Matulonis, G. I. Shapiro, R. S. Berkowitz, C. P. Crum and A. D. D'Andrea, *Cancer Discovery*, 2018, **8**, 1404–1421.
- 79 O. Kopper, C. J. de Witte, K. Löhmußaar, J. E. Valle-Inclan, N. Hami, L. Kester, A. V. Balgobind, J. Korving, N. Proost, H. Begthel, L. M. van Wijk, S. A. Revilla, R. Theeuwssen, M. van de Ven, M. J. van Roosmalen, B. Ponsioen, V. W. H. Ho, B. G. Neel, T. Bosse, K. N. Gaarenstroom, H. Vrieling, M. P. G. Vreeswijk, P. J. van Diest, P. O. Witteveen, T. Jonges, J. L. Bos, A. van Oudenaarden, R. P. Zweemer, H. J. G. Snippert, W. P. Kloosterman and H. Clevers, *Nat. Med.*, 2019, **25**, 838–849.

