# Chemical Science



### COMMENTARY

View Article Online View Journal | View Issue



Cite this: Chem. Sci., 2025, 16, 2480

d All publication charges for this article have been paid for by the Royal Society of Chemistry

DOI: 10.1039/d4sc90250e

rsc.li/chemical-science

# A focus on chasing pharmaceutical polyamorphs to design better oral drug formulations

Ana M. Belenguer 🕩

The pharmaceutical industry cares about reducing toxic side effects of drugs in oral formulation. The best solution is to reduce the drug dose. To do so, drugs are required to have high aqueous solubility to ensure good bioavailability. Amorphous drugs are much more water soluble than their crystalline counterparts, but can lack physical stability. Martins and Rades, et al. (I. C. B. Martins and T. Rades et al., Chem. Sci., 2023, 14, 11447-11455, DOI: https://doi.org/10.1039/D3SC02802J) demonstrate for the first time that polyamorphs (amorphous polymorphs) of drugs are now a reality. They demonstrated proof-of-concept, reproducible preparation methods for 3 polyamorphs (I, II and III) of hydrochlorothiazide (HCT) that display different glass transitions temperatures ( $T_{\rm q}$ ) and distinct structural relaxation profiles as excellent analytical indicators for discriminating between the polyamorphs. HCT polyamorph-II displayed improved physical stability with respect to the other HCT polyamorphs. A tangible benefit of polyamorphism research is the opportunity to select a specific polyamorph of a drug with the desired solubility and physical stability to be incorporated in an oral formulation, a strategy that should improve drug effectiveness.

The most obvious criterion between a medicinal or poisonous effect of any substance is its dose. Significantly lowering the dose of a drug in a medicinal formulation is the key to reducing the toxic side effects currently affecting many oral formulations prepared with crystalline drugs. Good bioavailability of drugs in oral formulations requires them to present good solubility in water as a surrogate measure of their solubility in aqueous body fluids. However, the solubility of crystalline materials is limited by their intermolecular long-range order, where high energy is required to disrupt

investigating a problematic but effective solution. Drug solubility is greatly improved by replacing poorly watersoluble crystalline forms for their amorphous forms. Unlike crystalline solids (Fig. 1, 1), amorphous solids lack longrange order (Fig. 1, 4). Amorphous solids are unambiguously identified

these interactions. The research community has been using differential scanning calorimetry

becomes rubbery (named a supercooled liquid/melt) and can even crystallise. Crystalline solids can be rendered amorphous by processes such as spray drying (SD), quench cooling (QC) and ball milling (BM). BM is the most commonly employed technique to prepare amorphous forms, but for drugs, only those with a  $T_g$  well above the ambient temperature can become amorphized by BM. If a drug compound has a lower  $T_g$ than the ambient temperature, it will become crystalline upon milling.2 Since BM is typically performed at ambient temperatures, and the temperature does not rise above 35 °C in long milling,2 not all drugs can be amorphized via BM. Alternative techniques for amorphization, including SD or QC,3-5 are currently the topic of research by Rades et al., as well as various analytical methods for the characterisation of the amorphous materials.6-8

> So, why are amorphous drugs problematic? As illustrated in Fig. 1,

> (DSC) on the emergence of the glass

transition temperature  $T_{\rm g}$ , as illustrated

in Fig. 1. Only below the  $T_g$  does the solid

stay in the amorphous state (also named

the glass state). Above the  $T_g$ , the solid

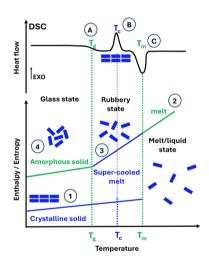


Fig. 1 Bottom: conceptual illustration of the energetic and organisational behaviour of 1 crystalline and 4 amorphous solids with respect to the increase in temperature. Starting from the 1 crystalline solid, the 2 melt/liquid state is obtained upon heating. From this @ melt/liquid state, on cooling down, a rubbery state is achieved in the 3 super-cooled melt, leading on further cooling to the 4 amorphous solid. Top: differential scanning calorimetry (DSC) profile for how a controllable increase or decrease in temperature produces (A) the glass transition temperature  $(T_q)$ , (B) an exothermic crystallisation temperature event  $(T_c)$ , and (C) an endothermic melt temperature event  $(T_m)$ 

Yusuf Hamied Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge, CB2 1EW, UK. E-mail: amb84@cam.ac.uk

Commentary

amorphous materials 4 have higher energy than their crystalline counterparts 1. This results in poor physical stability over time as they may become crystalline, therefore offering too short a shelf-life for commercialisation. The determination of structural relaxation of a freshly prepared amorphous material via isothermal microcalorimetry can be considered a surrogate indicator of its physical against crystallisation. All

amorphous materials will relax at some point, even if they do not crystallise on the experimental time scale.

What is blocking the rapid development of making amorphous drugs a pharmaceutical reality is the lack of suitable analytical tools to characterise their molecular-level organization. X-ray diffraction, so helpful for determining the molecular-level organisation of crystalline materials, is unsuitable in its

conventional way for amorphous materials. Powder X-ray diffraction (PXRD) scans are featureless for amorphous compounds, in comparison to crystalline species, which display distinct peaks (see Fig. 2a). While solid-state NMR can provide structural information on amorphous materials, conducting these experiments is very demanding. On the other hand, pair distribution functions (PDFs),10 and molecular dynamics (MD)

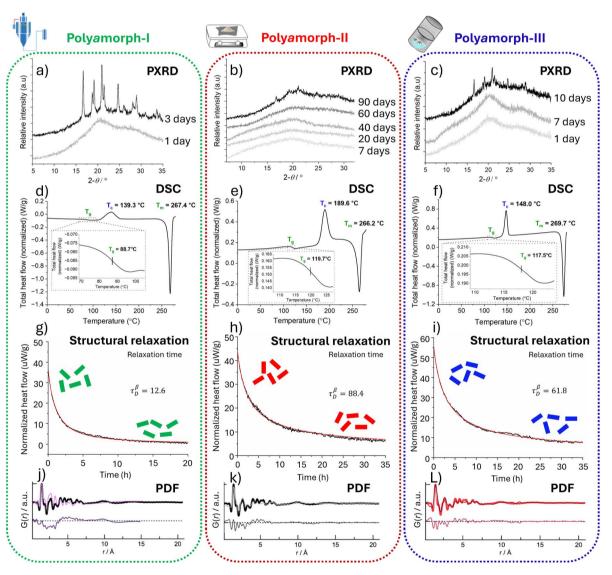


Fig. 2 Analytical data from powder X-ray diffraction (PXRD), differential scanning calorimetry (DSC), structural relaxation and pair distribution functions (PDFs); left column (a, d, g & j): polyamorph-I obtained by SD; middle column (b, e, h & k): polyamorph-II obtained by QC; and right column (c, f, i & I): polyamorph-III obtained by BM. Top row (a-c): superimposed PXRD scans of HCT polyamorph stability study. Polyamorph-II (b) has the highest physical stability while polyamorph-I (a) has the lowest, becoming crystalline 3 days after preparation. Second row down (d-f): DSC studies for all 3 polyamorphs: I, II and III are different as they present different  $T_{\rm g}$  and  $T_{\rm g}$  values. Third row down (g-i): the structural relaxation data showing significant differences between all 3 polyamorphs. Polyamorph-II (h) with the slowest relaxation  $\tau_{\rm h}^{\beta}=88.4$  will have the highest physical stability. Bottom row (j-I): PDF data (probability (G) of finding a pair of atoms at a given r distance), unambiguously demonstrating that for any of the 3 polyamorphs, there is no long-range order (range of >7 Å) corresponding to the intermolecular interactions. It also excludes the presence of crystalline and nanocrystalline material. The originals of all the graphs (ref. 9) were supplied by courtesy of Inês C. B. Martins to modify them as felt fit for the preparation of this figure.

Chemical Science Commentary

simulations,<sup>11</sup> are being explored to obtain some, though limited, understanding of the molecular-level organization of amorphous materials.

Several reports show that amorphous drugs, obtained using different preparation methods, display distinct physicochemical and thermal properties. This anecdotal data motivated Martins and Rades, *et al.* to work on dispelling the belief that polyamorphs of organic compounds are a fiction. Polyamorphism is defined as the formation of two or more amorphous forms of a single compound, separated by a phase transition. Page 13

For the first time, Martins and Rades, et al. performed a comprehensive and well-structured proof-of-concept investigation to demonstrate the unequivocal existence of 3 polyamorphs (I, II and III) of hydrochlorothiazide (HCT). Starting from crystalline HCT, polyamorph-I was prepared by SD, polyamorph-II by QC and polyamorph-III by BM. Interestingly, while polyamorph-I and III can be transformed to polyamorph-II by QC, it is not possible to transform polyamorph-II to polyamorph-I by SD and to polyamorph-III by BM.

Fig. 2 summarizes the 4 analytical techniques applied to characterise the 3 polyamorphs I, II and III.9 DSC supplies the characterising  $T_g$  and isothermal microcalorimetric analysis supplies the structural relaxation. These parameters unmistakably differentiate between the 3 HCT polyamorphs. Polyamorph-I with a  $T_g$  of 88 °C, polyamorph-II with a  $T_g$  of 119 °C, and polyamorph-III with a  $T_{\rm g}$  of 117.5 °C, have very different glass transition temperatures. A further confirmation that polyamorph-II and -III are different is that, on further heating, polyamorph-II reaches a crystallisation temperature  $(T_c)$  of 189 °C while polyamorph-III only reaches a T<sub>c</sub> of 148 °C.9

The differences in relaxation between the 3 polyamorphs are striking, as shown in Fig. 2. Polyamorph-II takes the longest to relax, making it the most physically stable HCT polyamorph.9 While PXRD and PDF do not discriminate between the different polyamorphs, as shown in Fig. 2, they are complementary analytical techniques that support that all 3 HCT polyamorphs are fully amorphous. PXRD can confirm the absence of crystalline material, but it cannot confirm the absence of nanocrystals. However, PDF analysis performed at high energy synchrotron facilities can confirm the total absence of crystals and even nanocrystals. PDF analysis confirms that there are no differences between the intramolecular and first-neighbour intermolecular interactions of the 3 HCT polyamorphs. The difference therefore lie at the long-range scale.

To make polyamorphism a reality, the scientific community needs to develop new analytical techniques, most likely combined with computational methods, to accurately determine the molecularlevel organization (in other words, the structure) of amorphous materials. In summary, it matters how the amorphous forms are prepared, as some polyamorphs will have better physicochemproperties than others. immediate benefit of in-depth studies of polyamorphism is obvious: discovering drug polyamorphs with improved solubility and physical stability. The future of polyamorphism should be bright with safer and more affordable oral formulations in the marketplace.

#### Author contributions

Article written by Ana M. Belenguer.

#### Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

I thank Inês C. B. Martins for allowing me to use the original figures from her publication (ref. 9) to design Fig. 2 and for the creation and offer of the TOC graphical abstract to be used in this focus article.

#### References

- 1 M. Descamps, J. F. Willart, E. Dudognon and V. Caron, *J. Pharm. Sci.*, 2007, **96**, 1398–1407.
- 2 A. M. Belenguer, A. J. Cruz-Cabeza, G. I. Lampronti and J. K. M. Sanders, CrystEngComm, 2019, 21, 2203–2211.
- 3 J. Liu, H. Grohganz, K. Löbmann, T. Rades and N.-J. Hempel, *Pharmaceutics*, 2021, **13**, 389.
- 4 J. E. Patterson, M. B. James,
  A. H. Forster, R. W. Lancaster,
  J. M. Butler and T. Rades, *J. Pharm. Sci.*, 2005, 9, 1998–2012.
- 5 G. Kasten, H. Grohganz, T. Rades and K. Löbmann, *Eur. J. Pharm. Sci.*, 2016, 95, 28–35.
- 6 M. M. Knopp, K. Löbmann, D. P. Elder, T. Rades and R. Holm, *Eur. J. Pharm. Sci.*, 2016, **87**, 164–173.
- N. Chieng, S. Rehder, D. Saville,
   T. Rades and J. Aaltonen, J. Pharm. Biomed. Anal., 2009, 49, 18–25.
- 8 K. T. Jensen, L. I. Blaabjerg, E. Lenz, A. Bohr, H. Grohganz, P. Kleinebudde, T. Rades and K. Löbmann, *J. Pharm. Pharmacol.*, 2016, **68**, 615–624.
- 9 I. C. B. Martins, A. S. Larsen,
  A. Ø. Madsen, O. A. Frederiksen,
  A. Correia, K. M. Ø. Jensen,
  H. S. Jeppesen and T. Rades, *Chem. Sci.*, 2023, 14, 11447-11455.
- 10 M. W. Terban and S. J. L. Billinge, *Chem. Rev.*, 2022, **122**, 1208–1272.
- 11 H. D. Özeren, R. T. Olsson, F. Nilsson and M. S. Hedenqvist, *Mater. Des.*, 2020, **187**, 108387.
- 12 K. Edueng, C. A. S. Bergström, J. Gråsjö and D. Mahlin, *Pharmaceutics*, 2019, **11**, 425.
- B. C. Hancock, E. Y. Shalaev and
   S. L. Shamblin, *J. Pharm. Pharmacol.*,
   2002, 54, 1151–1152.