


Showcasing research from Dr. Hajime Suzuki's group in Prof. Ryu Abe's laboratory, Graduate School of Engineering, Kyoto University, Japan.

Interlayer-active layered oxysulfides $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) with an $n = 1$ Ruddlesden-Popper structure acting as photocatalysts for visible light water splitting

This study reports the first synthesis of $n = 1$ Ruddlesden-Popper layered oxysulfides, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$). $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ is also the first example of an “interlayer-active” oxysulfide (*i.e.*, exhibiting ion exchange and interlayer hydration capabilities), with potential for visible-light-driven overall water splitting.

Image reproduced by permission of Hajime Suzuki from *Chem. Sci.*, 2025, **16**, 16534.

As featured in:

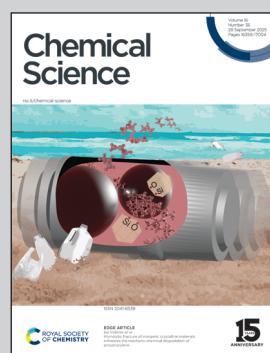

See Hajime Suzuki, Ryu Abe *et al.*, *Chem. Sci.*, 2025, **16**, 16534.

Cite this: *Chem. Sci.*, 2025, **16**, 16534 All publication charges for this article have been paid for by the Royal Society of Chemistry

Interlayer-active layered oxysulfides $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) with an $n = 1$ Ruddlesden–Popper structure acting as photocatalysts for visible light water splitting

Yusuke Ishii,  Hajime Suzuki,  * Daichi Kato,  Osamu Tomita,  Akinobu Nakada  and Ryu Abe  *

Layered compounds that utilize interlayer space as a reactive field are known as “interlayer-active” compounds and have been gaining attention, particularly in photocatalysis for water splitting. However, most of the reported “interlayer-active” photocatalysts are oxide semiconductors that possess a wide bandgap. Thus, they cannot utilize visible light essential for efficient water splitting. In this study, we synthesized novel Ruddlesden–Popper (RP) ($n = 1$) layered oxysulfides, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$), by heating “interlayer-active” layered oxides, NaMTiO_4 , under H_2S flow. In $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, the sulfur atoms occupy the apical oxygen sites and contribute to the elevated valence band maximum (VBM) to enable visible light absorption. Additionally, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ exhibits both proton exchange and interlayer hydration capabilities as well as photocatalytic activity for hydrogen and oxygen evolution under visible light. Hence, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ is the first example of both a $n = 1$ RP and an “interlayer-active” oxysulfide with the potential for visible-light-driven overall water splitting. The “interlayer-active” RP ($n = 1$) oxysulfide is expected to find application in various fields beyond photocatalysis by utilizing interlayer reactions such as ion exchange and interlayer hydration.

Received 1st July 2025
Accepted 13th August 2025DOI: 10.1039/d5sc04851f
rsc.li/chemical-science

Introduction

Layered oxides with functional interlayers have attracted considerable interest in fields such as energy storage,^{1–3} nanoelectronics,^{4–6} and photocatalysis.^{7–9} For instance, layered lithium cobalt oxide (LiCoO_2) is a widely used cathode material in Li-ion batteries because of its strong electromotive force and excellent charge–discharge characteristics due to its outstanding lithium-ion diffusion in the interlayers.^{1,10,11} Additionally, layered NaCoO_2 ^{12,13} and NaFeO_2 ,^{14,15} which contain Na ions in the interlayer, are the most promising materials for next-generation Na-ion batteries. In nanoelectronics, various nanosheets synthesized by exfoliating layered oxides have attracted significant attention owing to their high crystallinity, derived from the parent layered oxides, as well as their high designability and rich variety.^{4,16,17} For example, $\text{Ca}_2\text{Nb}_3\text{O}_{10}$ nanosheets, which are obtained by the exfoliation of layered $\text{HCa}_2\text{Nb}_3\text{O}_{10}$ by exchanging the H^+ ions in its interlayer for bulky tetrabutylammonium ions (TBA^+), reportedly function efficiently as a gate insulator.¹⁸ The low leakage current density and high dielectric constant of a dielectric thin film based on $\text{Ti}_{0.87}\text{O}_2$ nanosheets, derived from layered $\text{H}_{1.07}\text{Ti}_{1.73}\text{O}_4$, make it

suitable for application as a field-effect transistor.⁶ In the field of photocatalysis, it has been demonstrated that certain layered metal oxides, such as $\text{K}_4\text{Nb}_6\text{O}_{17}$ ¹⁹ and $\text{K}_2\text{La}_2\text{Ti}_3\text{O}_{10}$,⁹ which utilize their interlayer spaces as reaction sites for water splitting, are highly efficient photocatalysts for the overall water splitting reaction under UV light irradiation. The particles of common non-layered photocatalysts are several hundred nanometers in size, and photoexcited carriers must travel long distances to react with water molecules; in contrast, photoexcited carriers in layered oxides only travel within the 1–2 nm-thick metal oxide layer to react with water molecules in the interlayer. This enables the efficient utilization of photoexcited carriers in the reaction before recombination, with high quantum yields for water splitting under UV light.²⁰

More recently, research interest has extended to sulfides and oxysulfides.^{21–26} Owing to the lower electronegativity (and higher polarizability) of sulfur compared to that of oxygen, sulfides tend to form anionic frameworks with greater polarizability compared to oxides. This enhanced polarizability increases the ion conductivity and makes sulfides particularly attractive for use in metal-ion batteries.²² Moreover, many (oxy)sulfide semiconductors can absorb visible and near-infrared light because of the low electronegativity of sulfur. Consequently, these materials are actively applied in the fields of nanoelectronics and photocatalysis, *e.g.*, in phototransistors^{27,28} and

Department of Energy and Hydrocarbon Chemistry, Graduate School of Engineering, Kyoto University, Katsura, Nishikyo-ku, Kyoto 615-8510, Japan



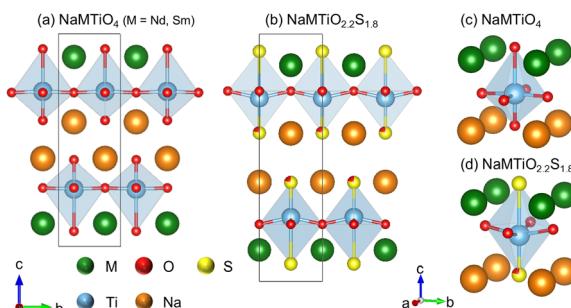


Fig. 1 Crystal structures of (a) NaMTiO₄ (M = Nd, Sm) and (b) NaMTiO_{2.2}S_{1.8}. (c and d) Enlarged views around the Ti–O(S) octahedra.

photodetectors^{24,29} sensitive to visible and near-infrared light, as well as in water-splitting photocatalysts for the generation of hydrogen from water under visible light.²⁵

The valence bands of (oxy)sulfide semiconductors are primarily composed of S-3p orbitals, which elevate the valence band maximum (VBM) to decrease the bandgaps compared to those of oxide semiconductors. In photocatalytic applications, many (oxy)sulfides have been developed as highly active hydrogen evolution photocatalysts upon irradiation with visible light.^{25,30,31} In particular, oxysulfide photocatalysts demonstrate higher stability against self-oxidation than sulfide photocatalysts, likely because of the partial contribution of O-2p orbitals to the valence band, which enables many of them to demonstrate activity for both water oxidation and reduction. In other words, the photogenerated holes are stably utilized for water oxidation rather than for oxidizing the sulfide anions (S²⁻) in oxysulfides (e.g., S²⁻ + 2h⁺ → S⁰). Indeed, M₂Ti₂O₅S₂ (M = Y, Sm, etc.) reportedly stably oxidizes water to oxygen under visible light.^{25,32,33} However, none of these oxysulfides possess “active interlayer spaces” that can function as reaction sites for water splitting. In fact, layered oxysulfides with both ion exchange and interlayer hydration capabilities, so-called “interlayer-active” oxysulfides, have not been reported to date.

In this study, we successfully synthesized Ruddlesden–Popper (RP) ($n = 1$) layered oxysulfides, NaMTiO_{2.2}S_{1.8} (M = Nd, Sm) (Fig. 1), by sulfurizing the “interlayer-active” layered oxide NaMTiO₄ as a precursor under H₂S flow. These compounds are the first examples of “interlayer-active” oxysulfides, and we demonstrated that they also function as photocatalysts for hydrogen/oxygen evolution under visible light. These “interlayer-active” RP ($n = 1$) oxysulfides are expected to find application beyond photocatalysis through ion-exchange reactions and interlayer hydration.

Results and discussion

Synthesis of new oxysulfides NaMTiO_{2.2}S_{1.8} via sulfurization of NaMTiO₄

RP NaMTiO₄ (M = Nd, Sm) was synthesized *via* a conventional solid-state reaction to serve as a precursor for sulfurization, as previously reported.³⁴ X-ray diffraction (XRD) analysis confirmed the presence of single-phase NaMTiO₄ (Fig. 2), which

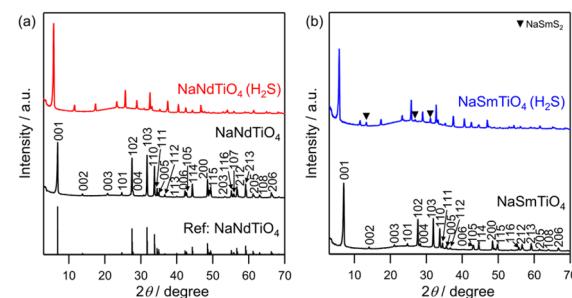


Fig. 2 XRD patterns of NaMTiO₄ (M = (a) Nd, (b) Sm) and the sulfurized product of the NaMTiO₄ (NaMTiO₄ (H₂S)), along with reference patterns of NaNdTiO₄ (ICSD #82004). Triangles denote the peaks of the byproduct NaSmS₂ (ICSD #644974).

was then heated at 1223 K for 2 h under H₂S flow (denoted as NaMTiO₄ (H₂S))). After sulfurization, the XRD pattern resembled that of the parent phase and could be indexed using the ideal tetragonal lattice as NaLaTiO₄ (*P4/nmm*), except for small byproduct peaks, such as those of NaSmS₂. However, the *c*-axis was extended significantly ($\Delta c \approx 2.4 \text{ \AA}$), whereas the *a*-axis did not change much (NaNdTiO₄: *a* $\approx 3.8 \text{ \AA}$, *c* $\approx 12.8 \text{ \AA}$ and NaNdTiO₄ (H₂S): *a* $\approx 3.9 \text{ \AA}$, *c* $\approx 15.2 \text{ \AA}$) (Fig. S1), strongly suggesting the successful substitution of O by the larger S atom at the apical site of the perovskite layer. A substantial amount of S was confirmed by energy dispersive X-ray spectroscopy (EDX) analysis (M = Nd : S/Ti = 1.73, M = Sm : S/Ti = 1.68) (Fig. S2, S3 and Table S1). Additionally, SEM images of NaMTiO₄ before and after sulfurization show no significant change in particle shape; the particles maintained a plate-like morphology (Fig. S4). These results support the formation of the new layered oxysulfide.

Fig. 3 shows the Rietveld refinement of the synchrotron X-ray powder diffraction (SXRPD) data. The structural models we constructed for the Rietveld refinement based on the NaLaTiO₄ structure (space group *P4/nmm*) (Fig. S5a and b) are not structurally distorted because the SXRPD pattern does not contain any superlattice peaks. In addition, the difference in the lattice parameters before and after sulfurization is similar to that of

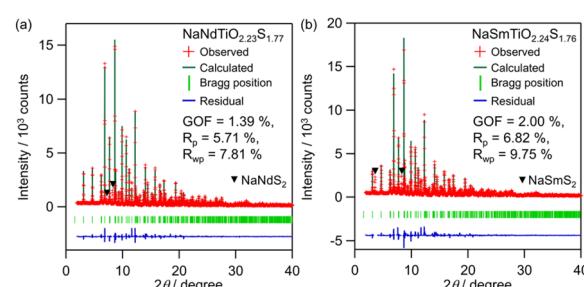


Fig. 3 Rietveld refinement against the SXRPD patterns of (a) NaNdTiO₄ (H₂S) and (b) NaSmTiO₄ (H₂S) using structural models of NaNdTiO_{2.23}S_{1.77} (Fig. S5a) and NaSmTiO_{2.24}S_{1.76} (Fig. S5b). The red crosses and the green and blue lines represent the observed, calculated, and difference intensities, respectively. Green ticks indicate calculated Bragg reflections. Triangles denote the peaks of the byproducts NaNdS₂ (ICSD #644913) and NaSmS₂.



the $n = 2$ RP oxide (e.g., $\text{Sr}_3\text{Ti}_2\text{O}_7$)³⁵ and oxysulfide (e.g., $\text{Y}_2\text{Ti}_2\text{O}_5\text{S}_2$)³⁶ where selective substitution of S at the apical site of the perovskite layer elongates the c -axis but does not affect the a -axis. Density functional theory (DFT) calculation, performed using the $\text{NaLaTiO}_{4-x}\text{S}_x$ structure without f -electrons to simplify the calculation, also supports the site selectivity of sulfur at the apical site in $\text{NaMTiO}_{4-x}\text{S}_x$ (see discussion in Fig. S6, S7 and Tables S2, S3). Therefore, we partially replaced the apical oxygen of the ideal NaLaTiO_4 structure with sulfur, refined all variable positional parameters, U_{iso} , and refined the occupancy of sulfur at the apical site. The occupancy of the S3 site adjacent to M converged to 1.11(2); hence, we fixed it at unity. On the other hand, the occupancy of S at the S2 site adjacent to the Na site converged to 80%, giving the composition of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$, which is consistent with the EDX result. The U_{iso} of Na1 converged to a large value of 0.04 \AA^2 . This large U_{iso} may indicate high mobility of Na in the sulfide layer due to weak Na–S interaction, as seen in sulfide-based alkali-ion conductors,^{37–39} such as Na_3PS_4 , which could be beneficial for ion-exchange reactions. The refinement yields a good fit with the reliability factors ($\text{M} = \text{Nd}$: $R_{\text{wp}} = 7.81\%$ and $\text{GOF} = 1.39$; $\text{M} = \text{Sm}$: $R_{\text{wp}} = 9.75\%$ and $\text{GOF} = 2.00$). The final crystallographic data (Tables S4 and S5) and profile after refinement (Fig. 3) correspond with the high-angle annular dark field scanning transmission electron microscopy (HAADF-STEM) and annular bright-field STEM (ABF-STEM) images along the [100] direction (Fig. 4a–c and S8). Additionally, the STEM-EDX line analysis supported selective occupation of sulfur at the apical sites of the perovskite layer (S2 and S3) (Fig. 4d and S9).

The structures of the $n = 1$ RP oxysulfides $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ (Fig. S5a and b) were compared with that of $\text{M}_2\text{Ti}_2\text{O}_5\text{S}_2$, which has a cation-deficient $n = 2$ RP structure, as other $n = 1$ RP oxysulfides have not yet been reported. Most of the Ti–O and Ti–S bond lengths are similar to those of $\text{M}_2\text{Ti}_2\text{O}_5\text{S}_2$ (Fig. S5c and d), confirming that the resolved structure is reasonable. Both apical sites of the Ti octahedra in $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ were occupied by sulfur, whereas only one of them in $\text{M}_2\text{Ti}_2\text{O}_5\text{S}_2$ was occupied by S, probably because the anion sites bridging the two octahedra were too small for sulfur to occupy. Notably, in $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, approximately 20% of the oxygen occupies the apical anion site on the Na layer side, resulting in the Ti–O₂/S₂ bond length being shorter than the typical Ti–O bond but longer than the typical Ti–S bond. Such a random occupation of O and

S at the same site is surprising given the Hume–Rothery rule, which states that anions with significantly different ionic radii, such as O^{2-} (1.4 Å) and S^{2-} (1.84 Å), generally cannot form solid solutions. The unusual occupation of O/S may be facilitated by the flexibility of the layered structure with weak interlayer interactions, such as that in BiOX ($\text{X} = \text{Cl}, \text{Br}, \text{I}$), which forms a solid solution between BiOCl and BiOI despite their distinctly different ionic radii (Cl : 1.81 Å, I : 2.2 Å).⁴⁰

NaMTiO_4 ($\text{M} = \text{La}, \text{Pr}, \text{Eu}, \text{Gd}, \text{Y}, \text{and Er}$) were also sulfurized using the same procedure as that for Nd and Sm (Fig. 5 and S10, S11). For those metals with intermediate ionic radii, $\text{NaMTiO}_{4-x}\text{S}_x$ ($\text{M} = \text{Pr}, \text{Eu}, \text{Gd}$) was obtained as the main phase, and its lattice parameters decreased nearly linearly with the decreasing ionic radius of M (Fig. S12), indicating the successful synthesis of a series of $\text{NaMTiO}_{4-x}\text{S}_x$. For La with the largest ionic radius, we observed a new peak at approximately 6°, which may correspond to $\text{NaLaTiO}_{4-x}\text{S}_x$; however, most peaks correspond to the perovskites $\text{Na}_{0.5}\text{La}_{0.5}\text{TiO}_3$ and NaLaS_2 (Fig. 5b and S11a). For the smaller M cations (Y and Er), sulfurization resulted in complete decomposition into the pyrochlore phases, $\text{M}_2\text{Ti}_2\text{O}_7$ and NaMS_2 (Fig. 5c and S11b, c). These observations indicate that the stability of competing oxides (perovskite and pyrochlore) is important for the successful formation of the oxysulfide $\text{NaMTiO}_{4-x}\text{S}_x$ (Table S6).

Although RP oxides are a large family of compounds, the RP oxysulfides reported thus far are very limited, with only a few examples of $n = 2$ cation-deficient $\text{M}_2\text{Ti}_2\text{O}_5\text{S}_2$ and $\text{M}_2(\text{MR})\text{O}_5\text{S}_2$ ($\text{M} = \text{lanthanoid}, \text{Y}; \text{R} = \text{Nb}$ and Ta). $\text{NaMTiO}_{4-x}\text{S}_x$ is the first reported oxysulfide with an $n = 1$ perovskite layer and A-site (Na/M) cation ordering, suggesting the possibility of expanding the oxysulfide RP family. The most notable feature of our new compounds is the presence of a rock salt layer composed of

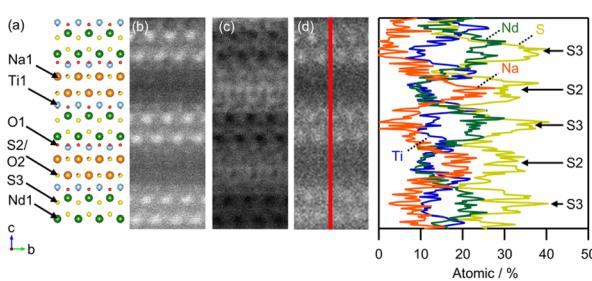


Fig. 4 STEM images of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$ in the [100] direction. (a) The crystal structure of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$. Enlargements of (b) HAADF and (c) ABF. (d) STEM-EDX line analysis of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$.

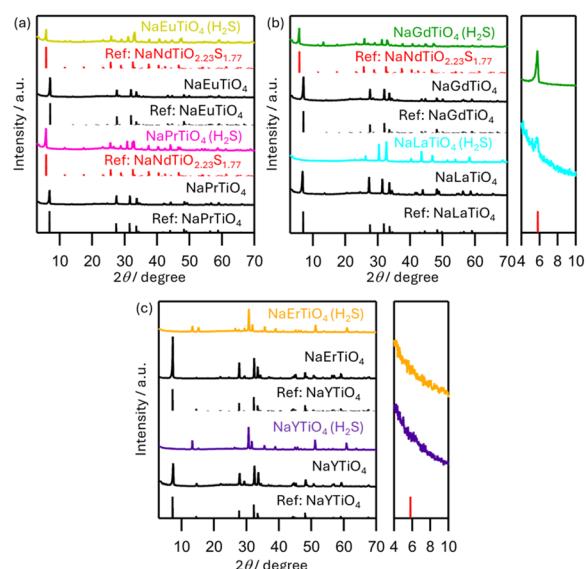


Fig. 5 XRD patterns of NaMTiO_4 ($\text{M} = \text{(a) Pr, Eu, (b) La, Gd, (c) Y, Er}$) and the sulfurized product of the NaMTiO_4 ($\text{NaMTiO}_4(\text{H}_2\text{S})$), along with the reference patterns of NaPrTiO_4 (ICSD #422048), NaEuTiO_4 (ICSD #79229), NaGdTiO_4 (ICSD #81537), NaLaTiO_4 (ICSD #422047), $\text{NaNdTiO}_{2.23}\text{S}_{1.77}$ (this work), and NaYTiO_4 (ICSD #81538).



mobile Na^+ ions. For oxide RP phases, the alkali metal layer allows ion exchange with various elements and molecules, as well as interlayer hydration, which confers unique functionalities. For example, replacing Na^+ in NaMTiO_4 ($\text{M} = \text{La, Nd}$) with H^+ , followed by substitution with a bulky cation such as TBA^+ , allows the fabrication of oxide nanosheets.⁴¹ Furthermore, ion-exchange reactions between alkali metals and transition metals can produce unique magnetic materials such as ferromagnetic $\text{Li}_{0.3}\text{Ni}_{0.85}\text{La}_2\text{Ti}_3\text{O}_{10}$.⁴² In addition to ion exchange, interlayer hydration can enhance the two-dimensional nature by expanding the interlayer distance with the emergence of interesting properties, such as the superconductivity of $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$ induced by H_2O intercalation.⁴³ This suggests that similar ion exchange, exfoliation, and interlayer hydration chemistry could be expected for $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, which potentially paves a new direction for the functional use of RP oxysulfides.

Herein, we experimentally confirmed the proton exchange and/or hydration capabilities in the interlayer of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$). After stirring in an aqueous HCl, the XRD patterns showed an evident shift of the (001) peak toward a lower angle (Fig. 6), indicating an increase in the interlayer distance. After HCl treatment, the lattice parameters became $a = 4.142(8)$ Å and $c = 16.31(4)$ Å for $\text{M} = \text{Nd}$ and $a = 4.136(9)$ Å and $c = 16.26(3)$ Å for $\text{M} = \text{Sm}$ (Fig. S13a and Table S7). The elongation of the c -axis ($\Delta c \approx 1.0$ Å) is comparable to the hydration of NaMTiO_4 ,^{44,45} indicating the intercalation of water molecules between the layers, along with partial H^+ exchange (e.g., in the form of H_3O^+). EDX analysis confirmed the proton exchange: the Na/Ti molar ratio decreased from 1.12 (Nd) and 1.06 (Sm) to 0.18 (Nd) and 0.11 (Sm) after stirring in an HCl solution (Table S8). In addition, vacuum drying shifted the peak toward a higher angle owing to dehydration. For the dehydrated samples, the peak appears at a higher angle compared to the (001) peak of the original $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, indicating a smaller c -axis lattice parameter ($\text{M} = \text{Nd}: \Delta c \approx 0.8$ Å, $\text{M} = \text{Sm}: \Delta c \approx 0.7$ Å) (Fig. S13b and Table S7). This difference also indicated the exchange of Na^+ in $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ for H^+ with its smaller ionic radius. H^+ exchange and hydration were also observed after stirring in distilled water, although the amount of residual Na is larger (0.27 for Nd and 0.18 for Sm) (Fig. 6 and Table S8). Additionally, in distilled water, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, especially $\text{M} =$

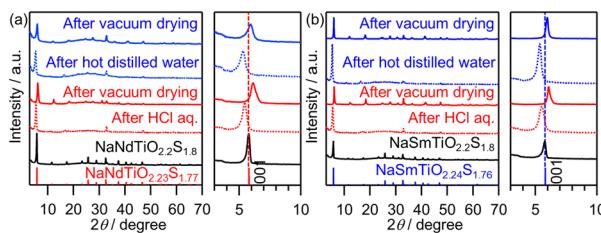


Fig. 6 XRD patterns of the sulfurized products, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) and the samples after stirring under dark conditions in an HCl aqueous solution for 24 h or hot distilled water for 72 h, followed by vacuum drying, along with the reference patterns of $\text{NaNdTiO}_{2.23}\text{S}_{1.77}$ (this work) and $\text{NaSmTiO}_{2.24}\text{S}_{1.76}$ (this work).

Sm, required a higher reaction temperature (Fig. S14). Based on the above findings, it has been confirmed that $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ is an “interlayer-active” oxysulfide, possessing both proton exchange and interlayer hydration capabilities.

Optical properties and band structures of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$)

The light absorption properties of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{NaMTiO}_4(\text{H}_2\text{S})$) ($\text{M} = \text{Nd and Sm}$) differed from those of the oxide precursor, NaMTiO_4 , after sulfurization, and the absorption edge shifted from approximately 340 nm to approximately 600 nm (Fig. 7a). Likewise, while the presence of impurities in the Pr, Eu, and Gd samples, these absorption edges shifted toward longer wavelengths (Fig. S15). The band levels of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) and NaMTiO_4 (Fig. 7b) were estimated based on a combination of the band gaps and flat-band potentials determined from the reflectance spectra and MS plots (Fig. S16), respectively. The flat-band potentials were assumed to be located just below the conduction band maxima (CBM) owing to the n-type nature of these materials. Although the CBMs of the oxysulfides were located at potentials similar to those of the precursor oxides, their VBM shifted significantly toward more negative potentials, rationalizing the significant decrease in the bandgap after sulfurization. The negative shift in the VBM was also confirmed by the ionization energies obtained using photoelectron yield spectroscopy (PYS) (Fig. S17). Importantly, these new oxysulfides possess appropriate band levels for both the reduction and oxidation of water under visible light irradiation.

The cause of the changes in the bandgaps was investigated by performing DFT calculations for the La-containing systems NaLaTiO_4 , $\text{NaLaTiO}_3\text{S}$, and $\text{NaLaTiO}_2\text{S}_2$ (Fig. 7c–e and S18), considering that these calculations for f-electron-containing systems are generally difficult. The calculated bandgap of $\text{NaLaTiO}_3\text{S}$ was narrower than that of NaLaTiO_4 and closely approximated that of $\text{NaLaTiO}_2\text{S}_2$ (Table S9). The Ti-3d orbitals

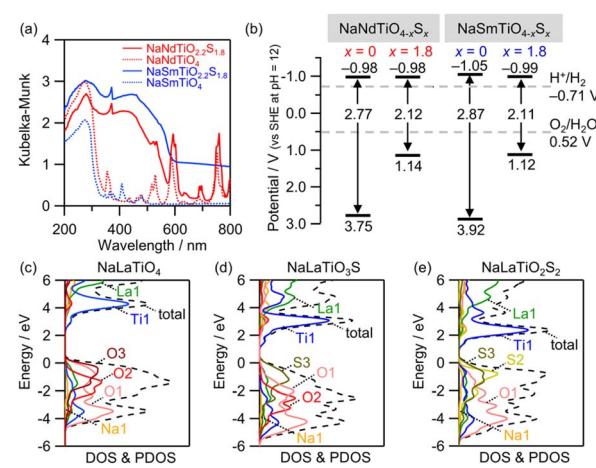


Fig. 7 (a) UV-vis diffuse reflectance spectra and (b) band edge positions at pH = 12 of NaMTiO_4 and $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$). DOS and PDOS near the VBM and CBM of (c) NaLaTiO_4 , (d) $\text{NaLaTiO}_3\text{S}$, and (e) $\text{NaLaTiO}_2\text{S}_2$ calculated using the structural models shown in Fig. S18.



mainly contribute to the density of states (DOS) around the CBM in all cases (Fig. 7c–e). The DOS around the VBM of NaLaTiO_4 was composed of O-2p orbitals, whereas those of $\text{NaLaTiO}_3\text{S}$ and $\text{NaLaTiO}_2\text{S}_2$ were mainly composed of S-3p orbitals in the S3 site adjacent to the La site, with additional contributions from the O-2p orbitals (Fig. S19). These results indicate that the narrow bandgap of the oxysulfide $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) is derived from the sizable contribution of the S-3p orbitals in the S3 site to the VBM.

Photocatalytic activity

The photocatalytic H_2 and O_2 evolution activities of the new $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) and NaMTiO_4 (H_2S) ($\text{M} = \text{Pr, Eu, Gd}$) samples were evaluated under visible light irradiation in the presence of electron donors and acceptors, respectively (Fig. 8 and S20). All the compounds exhibit steady H_2 evolution under visible light, with the activity of the Nd and Sm samples surpassing that of the others. This tendency is likely attributable to their higher phase purity. Their turnover numbers (TONs), defined as the number of moles of evolved H_2 divided by the number of moles of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, were 2.5 ($\text{M} = \text{Nd}$) and 1.2 ($\text{M} = \text{Sm}$), indicating that H_2 evolution proceeded photocatalytically. Notably, the oxide precursors NaMTiO_4 ($\text{M} = \text{Nd, Sm}$) generated no H_2 under visible light, indicating that bandgap narrowing *via* sulfurization rendered them responsive to visible light. The SEM images of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) after H_2 evolution revealed no changes (Fig. S21). The XRD patterns showed that, after the reaction, each of the two samples consisted of both the original $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ and the corresponding hydrated compound (Fig. S22), indicating that interlayer hydration, along with partial H^+ exchange, occurs during the reaction—an outcome similar to that when stirring in water in the dark. After the reaction, EDX of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) revealed that the Na/Ti ratio significantly decreased from 1.12 to 0.67 ($\text{M} = \text{Nd}$) and 1.02 to 0.52 ($\text{M} = \text{Sm}$), accompanied by a moderate decrease in the S/Ti ratio from 1.73 to 1.32 ($\text{M} = \text{Nd}$) and 1.68 to 1.43 ($\text{M} = \text{Sm}$), respectively (Table S10). This decrease in sulfur content is also supported by X-ray photoelectron spectroscopy (XPS) analysis (Fig. S23). Furthermore, the decrease in the Na/Ti and S/Ti ratios was also evident

after stirring in water in the dark ($\text{Na} : \text{Ti} : \text{S} = 0.56 : 1 : 1.29$ for $\text{M} = \text{Nd}$ and $0.46 : 1 : 1.34$ for $\text{M} = \text{Sm}$); thus, this compositional change proceeds chemically rather than photochemically. The above-mentioned DFT calculations and characterizations showed that the decrease in the Na/Ti and S/Ti ratios was due to proton exchange and S-to-O substitution at the $\text{S}_2(\text{O}_2)$ site in $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, respectively. Note that the S-to-O substitution at the $\text{S}_2(\text{O}_2)$ site alters the shape of the absorption spectrum but not the absorption edge (Fig. S24). Therefore, we concluded that the $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$) materials can function stably as photocatalysts, even after partial proton exchange and S-to-O substitution.

The evident O_2 evolution activity of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$ (contrary to its oxide precursors) confirmed its water-oxidation capability under visible light irradiation (Fig. 8b). The O_2 evolution was nonlinear, likely due to the photocatalytic oxidation of some sulfur species (*e.g.*, NaNdS_2) present on the photocatalyst surface. Enabling the oxysulfide $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$ to achieve overall visible-light-driven water splitting (*i.e.*, water splitting using a single photocatalyst) would require further optimization of the synthesis methods/conditions and appropriate surface modifications in the future. For example, enhancing crystallinity, controlling morphology, and tuning the exposed facets through flux synthesis may improve charge separation, thereby enhancing photocatalytic activity. Additionally, we expect interlayer modification (*e.g.*, loading a cocatalyst into the interlayer) of $\text{NaNdTiO}_{2.2}\text{S}_{1.8}$ to significantly improve its photocatalytic H_2 and O_2 evolution.

Conclusions

In conclusion, we successfully synthesized a novel RP ($n = 1$) oxysulfide, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, with an “interlayer-active” nature through sulfurization of the layered oxide NaMTiO_4 under H_2S gas. The sulfur primarily occupies the apical oxygen sites, and the sulfur atoms adjacent to M predominantly contribute to the elevated VBM to enable $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ to absorb visible light. This oxysulfide has both ion exchange and interlayer hydration capabilities, contrary to conventional RP oxysulfides such as $\text{M}_2\text{Ti}_2\text{O}_5\text{S}_2$, while also demonstrating photocatalytic hydrogen and oxygen evolution abilities under visible light irradiation. The discovery of an “interlayer-active” RP ($n = 1$) oxysulfide, $\text{NaMTiO}_{2.2}\text{S}_{1.8}$, enables new developments in various fields, including water splitting photocatalysis, *via* ion exchange reactions and interlayer hydration.

Experimental section

Materials

Na_2CO_3 (99.8%), La_2O_3 (99.99%), Nd_2O_3 (99.9%), Sm_2O_3 (99.9%), Eu_2O_3 (99.9%), Gd_2O_3 (99.9%), Er_2O_3 (99.9%), Y_2O_3 (99.99%), TiO_2 (anatase form, 98.5%), 1 M HCl aqueous solution (aq), $\text{RhCl}_3 \cdot 3\text{H}_2\text{O}$ (95.0–102.0%), Na_2S (98.0%), Na_2SO_3 (97.0%), AgNO_3 (99.8%), and 1 M NaOH aqueous solution (aq.) were purchased from the FUJIFILM Wako Pure Chemical Corporation. Pr_2O_3 (99.9%) was purchased from Kojundo

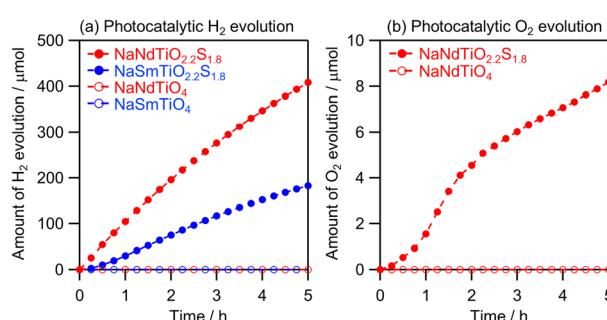


Fig. 8 Time courses of photocatalytic (a) H_2 and (b) O_2 evolution on NaMTiO_4 ($\text{M} = \text{Nd, Sm}$) and $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ from water with an electron donor (S^{2-} , SO_3^{2-}) and acceptor (Ag^+), respectively, under visible light ($400 < \lambda < 800 \text{ nm}$).



Chemical Laboratory Co., Ltd $\text{Na}_3\text{IrCl}_6 \cdot n\text{H}_2\text{O}$ (80.0%) was purchased from Kanto Chemical Co., Inc.

Sample synthesis

NaMTiO_4 samples ($\text{M} = \text{La, Pr, Nd, Sm, Eu, Gd, Er, and Y}$) were synthesized *via* solid-state reactions from a mixture of Na_2CO_3 , M_2O_3 , and TiO_2 in a molar ratio of $\text{Na} : \text{M} : \text{Ti} = 1.4 : 1 : 1$, according to a method reported previously.³⁴ The mixture was then calcinated in an alumina crucible at 1173–1323 K for 30 min in air (1173 K: $\text{M} = \text{La}$; 1273 K: $\text{M} = \text{Pr, Nd, Sm, Eu, Gd, Y}$; 1323 K: $\text{M} = \text{Er}$). $\text{NaMTiO}_{4-x}\text{S}_x$ (NaMTiO_4 (H_2S)) ($x = 1.8$; $\text{M} = \text{Nd, Sm}$) was synthesized by heating the obtained NaMTiO_4 samples at 1223 K for 2 h under flowing H_2S (flow rate: 50 ($\text{M} = \text{Sm}$) or 100 (other) mL min^{-1}).

The ion-exchange behavior of $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ was examined by stirring the compound for 24 h in an aqueous solution of HCl at room temperature (298 K) in the dark. The solution was prepared by adding 1 M aqueous HCl in distilled water in a molar ratio of $\text{H}^+ : \text{Na}^+ = 1 : 1$. To hydrate $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ ($\text{M} = \text{Nd, Sm}$), the synthesized $\text{NaMTiO}_{2.2}\text{S}_{1.8}$ was stirred in the dark for 72 h at room temperature (298 K) or in hot (333 K) distilled water, after which the products were collected *via* filtration and dried naturally. After drying, the samples were heated in a vacuum oven at 303 K.

Characterization

Powder XRD (PXRD; MiniFlex II, Rigaku, X-ray source: CuK_α), UV-visible diffuse reflectance spectroscopy (Shimadzu, UV-2600i), scanning electron microscopy (SEM; NVision 40, Carl Zeiss-SIINT) and scanning transmission electron microscopy (STEM; JEOL, JEM-ARM200CF) equipped with EDX were used to characterize the samples. Synchrotron X-ray diffraction (SXRD; BL02B2, SPring-8, Japan, $\lambda = 0.413922 \text{ \AA}$) patterns were collected at room temperature. Indexing of the SXRD patterns and Rietveld refinement were conducted using JANA2006.⁴⁶ The VESTA program was used to construct the crystal structures.⁴⁷ The ionization energy was directly measured by PYS (BIP-KV201, Bunkoukeiki) in a vacuum ($< 5 \times 10^{-2} \text{ Pa}$). Before the measurements, we calibrated the work function of a gold film (as a standard specimen), which corresponded to the Fermi energy from the vacuum level. X-ray photoelectron spectroscopy (XPS; JPS-9200, JEOL, X-ray source: $\text{Mg K}\alpha$) was employed for surface characterization. The XPS binding energies were calibrated using the $4f_{7/2}$ peak of Au (83.3 eV) deposited on the sample surface.

Electrochemical measurement

Mott–Schottky plots were recorded in a three-electrode cell equipped with a Pt wire counter-electrode and Ag/AgCl reference electrode in a phosphate-buffered solution (0.1 M, pH = 12.0) using an electrochemical analyzer (VersaSTAT 4, Princeton Applied Research) with an amplitude of 10 mV and a frequency of 1000 Hz. The electrodes were prepared using the squeegee method. A particulate sample containing a small amount of water was coated onto a fluorine-doped tin oxide (FTO) conductive substrate and dried overnight at room temperature.

DFT calculations

The electronic structures of NaLaTiO_4 , $\text{NaLaTiO}_3\text{S}$, and $\text{NaLaTiO}_2\text{S}_2$ were calculated using the Cambridge Serial Total Energy Package (CASTEP).⁴⁸ The calculated models of $\text{NaLaTiO}_3\text{S}$ and $\text{NaLaTiO}_2\text{S}_2$ assumed that O_3 site and the O_2 and O_3 sites, respectively, were fully occupied by S (Fig. S18). The Perdew–Burke–Ernzerhof functional for solids (PBEsol) generalized gradient approximation (GGA) was used as the exchange–correlation functional,⁴⁹ and the electronic states were expanded using a plane-wave basis set with a cut-off of 660 eV. The k -point meshes were set as $4 \times 4 \times 1$. Before the PDOS calculation, geometry optimization was performed using the Broyden–Fletcher–Goldfarb–Shannon (BFGS) algorithm.

Photocatalytic reactions

Photocatalytic reactions were carried out in a Pyrex glass reactor under an Ar flow (20 mL min^{-1}). The quantity of evolved gases was determined using an online gas chromatograph (GC 3210D, GL Sciences, thermal conductivity detector, column packing: 5 \AA molecular sieves, and Ar carrier gas). For the photocatalytic H_2 evolution, the photocatalyst powders (0.05 g) were suspended in 180 mL of an aqueous $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ solution (10 mM each), including $\text{RhCl}_3 \cdot 3\text{H}_2\text{O}$ as a precursor of the Rh cocatalyst (1 wt% as Rh metal). The photocatalysts were irradiated with visible light ($\lambda > 400 \text{ nm}$) using a cutoff filter (HOYA; L42) from a 300 W Xe-arc lamp (PerkinElmer, Cermax PE300BF). For the photocatalytic O_2 evolution, 0.05 g of IrO_2 -loaded photocatalysts was suspended in 180 mL of an aqueous AgNO_3 solution (10 mM, pH = 8.6, adjusted using 1 M NaOH aq.) with La_2O_3 (0.05 g) as a buffer and irradiated with visible light ($\lambda > 400 \text{ nm}$). IrO_2 (1 wt%) was loaded onto the photocatalyst powder through adsorption in a colloidal IrO_2 solution. IrO_2 colloids were prepared as reported previously.⁵⁰ The as-prepared powders were suspended in an aqueous solution containing the desired amount of IrO_2 colloids and stirred for 40 min. This procedure allowed the IrO_2 nanoparticles to be adsorbed onto the photocatalyst surface. The IrO_2 -loaded photocatalyst powder was collected *via* filtration and dried naturally. The TONs, defined as the number of moles of evolved H_2 at 5 h ($\text{NaNdTiO}_{2.23}\text{S}_{1.77}$: 408 μmol , $\text{NaSmTiO}_{2.24}\text{S}_{1.76}$: 183 μmol) divided by the number of moles of photocatalyst ($\text{NaNdTiO}_{2.23}\text{S}_{1.77}$: 163 μmol , $\text{NaSmTiO}_{2.24}\text{S}_{1.76}$: 159 μmol), were calculated to be 2.5 ($\text{NaNdTiO}_{2.23}\text{S}_{1.77}$) and 1.2 ($\text{NaSmTiO}_{2.24}\text{S}_{1.76}$), respectively.

Author contributions

Y. I. designed the study, with advice from H. S., D. K. and R. A. Rietveld refinements were initially performed by D. K. and then finalized by Y. I. All remaining experiments were performed by Y. I. All authors discussed the results; Y. I. wrote the manuscript and H. S. edited it, with discussions mainly with Y. I., H. S., D. K. and R. A.

Conflicts of interest

There are no conflicts to declare.



Data availability

All data are available in the main manuscript and the SI. XRD patterns, EDX, SEM images, crystal structures, structural analysis from Rietveld refinement, lattice parameters obtained via Le Bail analysis, HAADF-STEM images, STEM-EDX, calculated models and DOS&PDOS, PYS, UV-vis diffuse reflectance spectra and photocatalytic activities. See DOI: <https://doi.org/10.1039/d5sc04851f>.

Acknowledgements

This work was supported by the JSPS KAKENHI (JP20H00398 and JP23H02061) in grant-in-Aid for Scientific Research (A) and (B), respectively. This work was also supported by JST SPRING (JPMJSP2110) and JSPS Core-to-Core Program (JPJSCCA20200004). Synchrotron experiments were performed at SPring-8 BL02B2 of JASRI (2024B1972). A part of this study was supported by the Advanced Characterization Platform and AIST Nanocharacterization Facility (ANCF) Platform as a program of "Nanotechnology Platform" (JPMXP1224KU0041). We are also grateful to Mr Takaaki Toriyama of Kyushu University for his support with the STEM analysis. Computation time was provided by the SuperComputer System, Institute for Chemical Research, Kyoto University.

References

- 1 K. Mizushima, P. C. Jones, P. J. Wiseman and J. B. Goodenough, *Mater. Res. Bull.*, 1980, **15**, 783–789.
- 2 W. Zuo, A. Innocenti, M. Zarzabeitia, D. Bresser, Y. Yang and S. Passerini, *Acc. Chem. Res.*, 2023, **56**, 284–296.
- 3 J. B. Goodenough and Y. Kim, *Chem. Mater.*, 2010, **22**, 587–603.
- 4 M. Osada and T. Sasaki, *J. Mater. Chem.*, 2009, **19**, 2503–2511.
- 5 T. Taniguchi, L. Nurdwijayanto, R. Ma and T. Sasaki, *Appl. Phys. Rev.*, 2022, **9**, 021313.
- 6 S. Sekizaki, M. Osada and K. Nagashio, *Nanoscale*, 2017, **9**, 6471–6477.
- 7 Y. Okamoto, S. Ida, J. Hyodo, H. Hagiwara and T. Ishihara, *J. Am. Chem. Soc.*, 2011, **133**, 18034–18037.
- 8 T. Takata, Y. Furumi, K. Shinohara, A. Tanaka, M. Hara, J. N. Kondo and K. Domen, *Chem. Mater.*, 1997, **9**, 1063–1064.
- 9 T. Takata, K. Shinohara, A. Tanaka, M. Hara, J. N. Kondo and K. Domen, *J. Photochem. Photobiol. A*, 1997, **106**, 45–49.
- 10 J. Qian, L. Liu, J. Yang, S. Li, X. Wang, H. L. Zhuang and Y. Lu, *Nat. Commun.*, 2018, **9**, 4918.
- 11 S. Kalluri, M. Yoon, M. Jo, S. Park, S. Myeong, J. Kim, S. X. Dou, Z. Guo and J. Cho, *Adv. Energy Mater.*, 2017, **7**, 1601507.
- 12 J. Molenda, C. Delmas, P. Dordor and A. Stoklosa, *Solid State Ionics*, 1984, **12**, 473–477.
- 13 B. V. R. Reddy, R. Ravikumar, C. Nithya and S. Gopukumar, *J. Mater. Chem. A*, 2015, **3**, 18059–18063.
- 14 J. Zhao, L. Zhao, N. Dimov, S. Okada and T. Nishida, *J. Electrochem. Soc.*, 2013, **160**, A3077–A3081.
- 15 H. Watanabe, H. Usui, Y. Domi, T. Nishida, K. Uetake, T. Tanaka, H. Kurokawa and H. Sakaguchi, *ACS Electrochem.*, 2025, **1**, 73–81.
- 16 M. Osada, Y. Ebina, K. Takada and T. Sasaki, *Adv. Mater.*, 2006, **18**, 295–299.
- 17 H. Yim, S. Y. Yoo, Y. H. Kim, K. H. Chae, Y.-H. Kim, S. K. Kim, S.-H. Baek, C.-H. Lee and J.-W. Choi, *Chem. Mater.*, 2021, **33**, 8685–8692.
- 18 L. Kang, H. An, S. Jung, S. Kim, S. Nahm, D. Kim and C. G. Lee, *Appl. Surf. Sci.*, 2019, **476**, 374–377.
- 19 A. Kudo, K. Sayama, A. Tanaka, K. Asakura, K. Domen, K. Maruya and T. Onishi, *J. Catal.*, 1989, **120**, 337–352.
- 20 K. Sayama, A. Tanaka, K. Domen, K. Maruya and T. Onishi, *J. Catal.*, 1990, **124**, 541–547.
- 21 M. S. Whittingham, *Science*, 1976, **192**, 1126–1127.
- 22 Q. Zhang, D. Cao, Y. Ma, A. Natan, P. Aurora and H. Zhu, *Adv. Mater.*, 2019, **31**, e1901131.
- 23 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, *Nat. Nanotechnol.*, 2011, **6**, 147–150.
- 24 K. Ramakrishnan, B. Ajitha and Y. A. K. Reddy, *Sens. Actuators, A*, 2023, **349**, 114051.
- 25 Q. Wang, M. Nakabayashi, T. Hisatomi, S. Sun, S. Akiyama, Z. Wang, Z. Pan, X. Xiao, T. Watanabe, T. Yamada, N. Shibata, T. Takata and K. Domen, *Nat. Mater.*, 2019, **18**, 827–832.
- 26 Y. Kato, S. Hori, T. Saito, K. Suzuki, M. Hirayama, A. Mitsui, M. Yonemura, H. Iba and R. Kanno, *Nat. Energy*, 2016, **1**, 16030.
- 27 H. Xu, J. Wu, Q. Feng, N. Mao, C. Wang and J. Zhang, *Small*, 2014, **10**, 2300–2306.
- 28 Y. Kim, E. Jeong and C. Lee, *ACS Appl. Electron. Mater.*, 2024, **6**, 7883–7889.
- 29 Y. Yang, S. Liu, X. Wang, Z. Li, Y. Zhang, G. Zhang, D. Xue and J. Hu, *Adv. Funct. Mater.*, 2019, **29**.
- 30 A. Ishikawa, T. Takata, J. N. Kondo, M. Hara, H. Kobayashi and K. Domen, *J. Am. Chem. Soc.*, 2002, **124**, 13547–13553.
- 31 L. Lin, Y. Ma, J. J. M. Vequizo, M. Nakabayashi, C. Gu, X. Tao, H. Yoshida, Y. Pihosh, Y. Nishina, A. Yamakata, N. Shibata, T. Hisatomi, T. Takata and K. Domen, *Nat. Commun.*, 2024, **15**, 397.
- 32 H. Yoshida, Z. Pan, R. Shoji, V. Nandal, H. Matsuzaki, K. Seki, L. Lin, M. Kaneko, T. Fukui, K. Yamashita, T. Takata, T. Hisatomi and K. Domen, *Angew. Chem., Int. Ed.*, 2023, **62**, e202312938.
- 33 L. Lin, P. Kaewdee, V. Nandal, R. Shoji, H. Matsuzaki, K. Seki, M. Nakabayashi, N. Shibata, X. Tao, X. Liang, Y. Ma, T. Hisatomi, T. Takata and K. Domen, *Angew. Chem., Int. Ed.*, 2023, **62**, e202310607.
- 34 R. E. Schaak and T. E. Mallouk, *J. Solid State Chem.*, 2001, **161**, 225–232.
- 35 M. M. Elcombe, E. H. Kisi, K. D. Hawkins, T. J. White, P. Goodman and S. Matheson, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1991, **47**, 305–314.
- 36 C. Boyer-Candalen, J. Derouet, P. Porcher, Y. Moëlo and A. Meerschaut, *J. Solid State Chem.*, 2002, **165**, 228–237.
- 37 A. Hayashi, K. Noi, A. Sakuda and M. Tatsumisago, *Nat. Commun.*, 2012, **3**, 856.



38 N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto and A. Mitsui, *Nat. Mater.*, 2011, **10**, 682–686.

39 A. Hayashi, N. Masuzawa, S. Yubuchi, F. Tsuji, C. Hotehama, A. Sakuda and M. Tatsumisago, *Nat. Commun.*, 2019, **10**, 5266.

40 J. Xie, Y. Cao, D. Jia and Y. Li, *J. Colloid Interface Sci.*, 2017, **503**, 115–123.

41 S. A. Kurnosenko, I. A. Minich, O. I. Silyukov and I. A. Zvereva, *Nanomaterials*, 2023, **13**, 3052.

42 D. Neiner, L. Spinu, V. Golub and J. B. Wiley, *Chem. Mater.*, 2006, **18**, 518–524.

43 K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian and T. Sasaki, *Nature*, 2003, **422**, 53–55.

44 K. Toda, Y. Kameo, S. Kurita and M. Sato, *Bull. Chem. Soc. Jpn.*, 1996, **69**, 349–352.

45 I. A. Zvereva, O. I. Silyukov and M. V. Chislov, *Russ. J. Gen. Chem.*, 2011, **81**, 1434.

46 V. Petricek, M. Dusek and L. Palatinus, *Z. Kristallogr.–Cryst. Mater.*, 2014, **229**, 345–352.

47 K. Momma and F. Izumi, *J. Appl. Crystallogr.*, 2011, **44**, 1272–1276.

48 S. J. Clark, M. D. Segall, C. J. Pickard, P. J. Hasnip, M. I. J. Probert, K. Refson and M. C. Payne, *Z. Kristallogr.–Cryst. Mater.*, 2005, **220**, 567–570.

49 G. I. Csonka, J. P. Perdew, A. Ruzsinszky, P. H. T. Philipsen, S. Lebègue, J. Paier, O. A. Vydrov and J. G. Ángyán, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2009, **79**, 155107.

50 C. L. Paven-Thivet, A. Ishikawa, A. Ziani, L. L. Gendre, M. Yoshida, J. Kubota, F. Tessier and K. Domen, *J. Phys. Chem. C*, 2009, **113**, 6156–6162.