

# Chemical Science

rsc.li/chemical-science



ISSN 2041-6539

**EDGE ARTICLE**

Selvan Demir *et al.*

A tetraazanaphthalene radical-bridged dysprosium  
single-molecule magnet with a large coercive field

Cite this: *Chem. Sci.*, 2025, 16, 20806

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 18th July 2025  
Accepted 13th September 2025

DOI: 10.1039/d5sc05358g

rsc.li/chemical-science

## Introduction

The rapid advancements in artificial intelligence and cloud computing exert significant pressure on existing permanent storage media for digital data.<sup>1,2</sup> The development of new functional magnetic materials is essential to ensure that magnetic storage capacity continues to evolve in parallel with increasing data storage demands. To replace bulk magnetic materials like SmCo<sub>5</sub> and Nd<sub>2</sub>Fe<sub>14</sub>B,<sup>3–5</sup> one of the holy grails of quantum information science has revolved around the storage and manipulating of information in spin orientations on bits of the smallest conceivable unit – a single molecule.<sup>6,7</sup> However, to date molecular materials that retain magnetic information at high, ideally room temperature have remained elusive.

To this end, lanthanide ions play a crucial role, since their large unquenched orbital momentum and large spin-orbit coupling generate huge single-ion magnetic anisotropies when placed in a suitable crystal field, a circumstance in fact unparalleled in the periodic table. Trivalent dysprosium is highly anisotropic and possesses a doubly degenerate ground state due to its Kramers' ion electronic structure, rendering it particularly

# A tetraazanaphthalene radical-bridged dysprosium single-molecule magnet with a large coercive field

Florian Benner,<sup>1</sup> Saroshan Deshapriya<sup>1</sup> and Selvan Demir<sup>1\*</sup>

Generating strong magnetic coupling poses a fundamental challenge in the design of multinuclear lanthanide complexes. The inherently contracted nature of the valence 4f orbitals precludes the lanthanides from engaging in covalent bonding with closed-shell ligands. The employment of open-shell bridging ligands instead allows efficient interaction of the diffuse radical spin orbitals with the 4f shell of the lanthanides. Herein, we introduce the azaacene ligand, 1,4,5,8-tetraazanaphthalene (tan), into rare earth chemistry: first, we synthesized [(Cp\*<sub>2</sub>Dy)(μ-tan)] (1, Cp\* = pentamethylcyclopentadienyl) containing a diamagnetic tan<sup>2-</sup> bridge from a salt metathesis reaction of Cp\*<sub>2</sub>DyBPh<sub>4</sub> and K<sub>2</sub>(tan). Second, we chemically oxidised 1 to [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-tan<sup>1•-</sup>)] [BARF<sub>20</sub>] (2) comprising a tan<sup>1•-</sup> radical bridge. 2 is a rare radical-bridged single-molecule magnet (SMM) with open hysteresis loops below 3.75 K with a maximum coercive field (*H<sub>C</sub>*) of 1.373 T at 1.8 K, which represents a notable record as *H<sub>C</sub>* is approximately doubled compared to all known dinuclear lanthanide SMMs innate to organic radical bridges. A close match of the tan<sup>1•-</sup>/tan<sup>2-</sup> and Dy<sup>III</sup>/Dy<sup>II</sup> redox potentials may be the origin for the impressive hysteresis loops at low temperatures, while the magnetic behaviour at higher temperatures is likely impacted from spin-phonon coupling. The outlined design strategy of matching reduction potentials of the ligand with the metal ions to amplify magnetic coupling, was proposed *via* prior computations, but is within this study for the first time experimentally confirmed. In sum, highly-tunable azaacene radicals have immense potential not only for radical-containing SMMs but for high-performance magnetic materials at large.

relevant for single-molecule magnet (SMM) design.<sup>8,9</sup> A synthetic challenge to overcome is to couple strongly dysprosium ions to one another which due to the deeply buried 4f shell necessitates to place an unpaired electron with diffuse spin

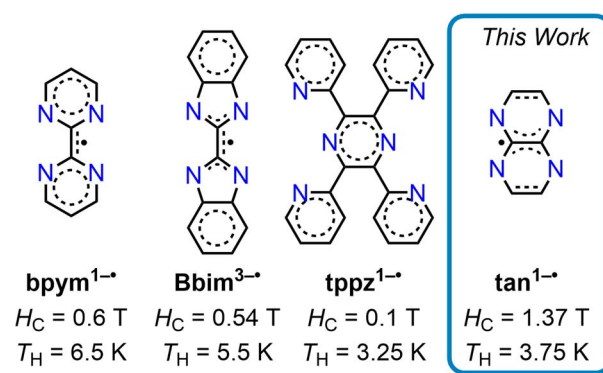


Fig. 1 Selected radical ligands used to construct dinuclear dysprosium single-molecule magnets [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-L)]X with coercive fields (*H<sub>C</sub>*) and open magnetic hysteresis loops at or below this temperature (*T<sub>H</sub>*) under conventional sweep rates. Ligands L are: bpym = 2,2'-bipyrimidine (X = BPh<sub>4</sub><sup>-</sup>), Bbim = 2,2'-bisbenzimidazole (X = [K(crypt-222)]<sup>+</sup>, crypt-222 = 2.2.2-cryptand), tppz = 2,3,5,6-tetra(2-pyridyl)pyrazine (X = BPh<sub>4</sub><sup>-</sup>), tan = 1,4,5,8-tetraazanaphthalene (X = BARF<sub>20</sub><sup>-</sup>).

Department of Chemistry, Michigan State University, East Lansing, Michigan 48824, USA. E-mail: sdemir@chemistry.msu.edu





recrystallised from toluene (KN(Si(CH<sub>3</sub>)<sub>3</sub>)<sub>2</sub>) and <sup>n</sup>hexane (crypt-222), respectively. KCP<sup>+</sup>,<sup>48</sup> [HNEt<sub>3</sub>][BPh<sub>4</sub>],<sup>49</sup> Cp<sup>+</sup><sub>2</sub>Dy(BPh<sub>4</sub>)<sup>+</sup>,<sup>48</sup> and KC<sub>8</sub><sup>50</sup> were synthesised according to literature procedures. 1,4,5,8-tetraazaphthalene (tan<sup>0</sup>) was synthesised *via* condensation of 2,3-diaminopyrazine with glyoxal in H<sub>2</sub>O according to literature procedures,<sup>43,45</sup> and the yellow precipitate was subsequently extracted *via* a Soxhlet apparatus with acetone overnight. Upon cooling to room temperature, tan<sup>0</sup> crystallised as yellow needles and, after drying under vacuum for several hours, was used without further purification. [Thian<sup>+</sup>][BARF<sub>20</sub>] was quantitatively obtained *via* a salt metathesis reaction of K[BARF<sub>20</sub>] with [Thian<sup>+</sup>][SbCl<sub>6</sub>]<sup>51,52</sup> in DCM in analogy to a procedure reported for [Thian<sup>+</sup>][Al{OC(CF<sub>3</sub>)<sub>3</sub>}<sub>4</sub>], and isolated through precipitation in <sup>n</sup>hexane and used without further purification.<sup>53</sup>

Single-crystal XRD data on **1** and **2** were collected on a XtaLAB Synergy DualflexHyPix four-circle diffractometer, equipped with a HyPix Hybrid Pixel Array Detector. The crystals were suspended in <sup>n</sup>paratone oil and mounted on a nylon loop. The temperature during data collection was controlled *via* an Oxford Cryosystems low-temperature device and kept at 100 K during the measurements for all compounds. Data were measured using  $\omega$  scans using CuK <sub>$\alpha$</sub>  radiation (microfocus sealed X-ray tube, 50 kV, 1 mA). The CrysAlisPro software package<sup>54</sup> was used to determine the total number of runs and images, to retrieve and refine the cell parameters, and for data reduction. A numerical absorption correction based on Gaussian integration over a multifaceted crystal model empirical absorption correction employing spherical harmonics was accomplished using the SCALE3 ABSPACK<sup>55</sup> scaling algorithm (spherical harmonics and frame scaling). The structures were solved with the ShelXT<sup>56</sup> structure solution program using intrinsic phasing and refined with version 2018/3 of ShelXL<sup>57</sup> using least squares minimisation as implemented in Olex2.<sup>58</sup> All non-hydrogen atoms are refined anisotropically. Hydrogen atoms were calculated by geometrical methods and refined as a riding model. The crystals used for the diffraction study showed no decomposition during data collection. Crystal data and structure refinement for **1** and **2** are depicted in Table S1.

IR spectra were taken with an Agilent Cary 630 ATR spectrometer residing in a nitrogen-filled glove bag.

UV-vis spectra were collected in an argon-filled glovebox using 1 cm cuvettes with an Agilent Cary 60 spectrometer, equipped with QP600-1-SR fibre optics and a Square One cuvette holder from Ocean Insight. Solvents and concentrations were 32  $\mu\text{mol L}^{-1}$  in DCM (**1**) and 140/40  $\mu\text{mol L}^{-1}$  in DCM (**2**).

Cyclic voltammetry experiments were carried out in an argon-filled glovebox deploying a PGSTAT204 potentiostat from Metrohm. A three-electrode setup involving a glassy carbon working electrode, platinum spring counter electrode, and silver wire reference electrode was used. All measurements were performed cycling the solvent range four-fold at a 100 mV s<sup>-1</sup> scan rate and  $E_{1/2}$  averaged, where all voltammograms displayed in the main text constitute the second scan. Due to chemical incompatibility of the organometallic complexes with ferrocene, the measurements were externally referenced to ferrocene solutions with identical supporting electrolyte concentrations

and electrode setup. Compounds **1** and **2** were measured as 3 mmol L<sup>-1</sup> DCM solutions. For all measurements, 220 mmol L<sup>-1</sup> electrolyte concentrations of (<sup>n</sup>Bu<sub>4</sub>N)PF<sub>6</sub> were used.

Elemental analysis was carried out with a PerkinElmer 2400 Series II CHNS/O analyser. The crystalline compounds of all samples (~1–3 mg) were weighed into tin sample holders and folded multiple times to ensure proper sealing from the surrounding atmosphere. The samples were then transferred to the instrument under exclusion of air in a sealed container.

Magnetic susceptibility data were collected on a Quantum Design MPMS3 Superconducting Quantum Interference Device (SQUID) magnetometer. The magnetic samples of [(Cp<sup>+</sup><sub>2</sub>Dy)<sub>2</sub>( $\mu$ -tan)] (**1**) and [(Cp<sup>+</sup><sub>2</sub>Dy)<sub>2</sub>( $\mu$ -tan')][BARF<sub>20</sub>] (**2**) were prepared by saturating and covering dried, crushed crystalline solids (14.2 mg (**1**), 21.6 mg (**2**)) with molten eicosane (26.2 mg (**1**), 35.1 mg (**2**)) at 50 °C to prevent crystallite torquing and to provide good thermal contact between the sample and the bath. The samples were sealed airtight and transferred to the magnetometer. The core diamagnetism for both samples were estimated using Pascal's constants.<sup>59</sup>

AC relaxation data were fit using the CCFIT2 program.<sup>60</sup> DC relaxation data were fit to a stretched exponential according to eqn (1) using the Origin 9.0.0 b45 software:

$$M(t) = M_{\text{eq}} + (M_0 - M_{\text{eq}}) \exp(-(t/\tau)^\beta) \quad (1)$$

where  $M_0$  is the initial magnetisation,  $M_{\text{eq}}$  is the last fit point ( $0.01M_0$ ),  $\beta$  the stretch factor and  $\tau$  the relaxation time.

Crystal coordinates of **1** and **2** were geometry optimised using TPSSh functional at def2-TZVP theory level.<sup>61</sup> For Dy<sup>III</sup> ions, the 4f-in-core potential Stuttgart–Cologne pseudopotential ECP55MWB and the associated ECP55MWB-II basis set were used.<sup>62–65</sup> Optimised coordinates were used for calculating TD-DFT transitions using the TPSS0 functional and CPCM DCM solvent model. Predicted transitions were shifted by 0.34 eV and 0.42 eV for **1** and **2**, respectively, to better match with their experimental UV-vis spectra. For the calculation of estimated exchange coupling, unrestricted density functional theory (DFT) calculations were carried out for a model system of **2** as described below. Crystal coordinates of the heavy atoms for all three molecular units (edge-centred unit and the two disorder parts of the face-centred unit) were used, Dy substituted for diamagnetic Lu, and H atom positions optimised on the DKH-def2-SVP level (SARC2-DKH-QZVP for Lu) using the TPSSh functional with D3BJ dispersion correction.<sup>66–71</sup> Subsequently, Lu atoms were substituted with Gd for broken-symmetry calculations. These model systems were employed to approximate the exchange coupling strength using the flipspin feature of the ORCA 5.0.4 software.<sup>72–74</sup> The spin lying on the tan bridge was flipped and the calculations were conducted using the TPSS0 functional at the def2-TZVP theory level.<sup>68,69</sup> The DKH-def2-TZVP basis set<sup>75</sup> was used for all atoms and segmented all-electron relativistically contracted (SARC) basis set with quadruple-zeta quality (SARC2-DKH-QZVP) was employed for Gd,<sup>67</sup> together with the Douglas–Kroll–Hess (DKH) Hamiltonian to account for scalar relativistic effects. The resolution of identity (RI) approximation was used for the Coulomb integrals



with the SARC/J auxiliary basis set, while the exchange integrals were treated with the chain-of-spheres approximation (COSX). Grimme's dispersion correction with Becke–Johnson damping (D3BJ) was applied for all calculations.<sup>70,71</sup> The generation of the spin density and molecular orbital distributions was accomplished employing the *orca\_plot* module and the VMD program was used for orbital visualisations.<sup>76</sup>

### Synthesis of [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-tan)] (1)

In a 7 mL scintillation vial, KC<sub>8</sub> (25.7 mg, 0.1901 mmol) was added to a THF (3 mL) suspension of tan<sup>0</sup> (12.5 mg, 0.0946 mmol), resulting in an immediate colour change from yellow to black, and the mixture was stirred for 30 min. The reduced tan species, presumably of a dianionic nature, was transferred *via* glass pipette into a 20 mL scintillation vial containing a stirring THF solution (~5 mL) of Cp\*<sub>2</sub>Dy(BPh<sub>4</sub>) (142.5 mg, 0.1894 mmol). Upon addition of K<sub>2</sub>tan, an immediate colour change from pale yellow to intense dark red was observed. The mixture was diluted with THF (resulting in a ~12 mL solution in total), and, upon stirring at room temperature for 1 h, the colour gradually turned to a lighter red. After stirring for further 15 h, the mixture was filtered through a Celite plug, to remove grey insoluble solids, presumably graphite and KBPh<sub>4</sub>. The solids were washed twice with THF (~2 mL) and the washings were filtered and combined with the main filtrate. The sum filtrate was evaporated to dryness, affording a red amorphous solid which was extracted with portions of toluene (~12 mL in total), filtered through a Celite plug, and the clear red filtrate was evaporated to dryness. The resulting red solid was redissolved in ~6 mL of hot toluene (60 °C), filtered hot through a Celite plug, and once cooled to room temperature, the clear, red filtrate was further cooled in the freezer for crystallisation. Dark red crystals of **1** suitable for single-crystal X-ray diffraction analysis were grown at –35 °C over the course of four days. The crystals were separated from the mother liquor, washed twice with cold toluene (~2 mL in total), and dried under vacuum for 2 h, yielding a dark red crystalline material of **1** (39.1 mg, 0.0392 mmol, 41%). Dried crystals of **1** are stable at room temperature under an inert Ar atmosphere for several months but quickly degrade under ambient atmosphere. Anal. Calcd for C<sub>46</sub>H<sub>64</sub>Dy<sub>2</sub>N<sub>4</sub> (**1**): C, 55.95; H, 6.53; N, 5.67; found: C, 55.83; H, 6.26; N, 5.77. IR (ATR, cm<sup>-1</sup>): 2963 (vw), 2902 (m), 2853 (m), 1769 (vw), 1739 (vw), 1541 (w), 1491 (vw), 1429 (vs), 1409 (vs), 1377 (vs), 1360 (m), 1217 (vw), 1202 (vw), 1169 (vs), 1094 (vw), 1060 (vw), 1019 (w), 880 (vw), 800 (vw), 751 (s), 729 (vw). λ<sub>max</sub> (nm, ε in 10<sup>4</sup> L mol<sup>-1</sup> cm<sup>-1</sup>): 288 (1.98), 295 (1.97), 487 (0.42), 520 (0.58), 561 (0.48).

### Synthesis of [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-tan')][BARF<sub>20</sub>] (2)

In a 20 mL scintillation vial, a solution of [Thian']<sub>2</sub>[BARF<sub>20</sub>] (40.0 mg, 0.0445 mmol, 1 mL DCM) was added to a stirred solution of **1** (40.2 mg, 0.0403 mmol) in DCM (3 mL), resulting in an immediate colour change from red to black. The mixture was slightly diluted with DCM (final volume: 5 mL), and then stirred at room temperature for 20 min. The reaction mixture was evaporated to dryness under stirring to yield a black solid

which was extracted three times with toluene (by using ~8 mL in total) and removed an unidentified orange byproduct. The toluene insoluble solids were dried under vacuum for 2 h, dissolved in DCM (~2 mL) and then layered with <sup>n</sup>hexane (~1 : 1 DCM/<sup>n</sup>hexane ratio) and cooled to –35 °C for crystallisation. Black crystals of **2** suitable for single-crystal X-ray diffraction analysis were grown at –35 °C over the course of 3 days. After removing the weakly coloured mother liquor, the crystals were washed twice with a 1 : 1 DCM/<sup>n</sup>hexane mixture (~0.5 mL each) and then dried under vacuum for 2 h, yielding black crystalline material of **2** (53.3 mg, 0.0318 mmol, 79%). Dried crystals of **2** are stable at –35 °C under an inert Ar atmosphere for several months. Anal. Calcd for C<sub>70</sub>H<sub>64</sub>BDy<sub>2</sub>F<sub>20</sub>N<sub>4</sub> (**2**): C, 50.13; H, 3.85; N, 3.34; found: C, 49.93; H, 3.81; N, 3.27. IR (ATR, cm<sup>-1</sup>): 2913 (vw), 2905 (vw), 2864 (vw), 1642 (vw), 1511 (m), 1487 (w), 1461 (vs), 1392 (w), 1379 (m), 1275 (w), 1269 (w), 1195 (m), 1085 (s), 1019 (vw), 977 (vs), 913 (vw), 898 (vw), 822 (m), 773 (m), 755 (s), 740 (vw), 725 (vw), 682 (m), 660 (s). λ<sub>max</sub> (nm, ε in 10<sup>4</sup> L mol<sup>-1</sup> cm<sup>-1</sup>): 355 (1.34), 649 (0.14), 682 (0.15), 716 (0.17), 797 (0.16).

## Results and discussion

### Synthesis, structural and spectroscopic characterisation

The synthesis of tan radical-bridged lanthanide complexes was inspired by our deployed strategy to gain access to a flv<sup>1-•</sup> radical-bridged metal complex, by generating first a neutral molecule composed of a diamagnetic flv<sup>2-</sup> bridge followed by chemical oxidation.<sup>42</sup> In contrast to flv, tan lacks NH protons and thus the diamagnetic tan<sup>2-</sup> was pursued *via* chemical reduction.

First, a THF suspension of tan<sup>0</sup> was treated with two equivalents of KC<sub>8</sub> to yield a black suspension which was used *in situ* by a quantitative transfer onto a stirring pale yellow THF solution comprising two equivalents of Cp\*<sub>2</sub>Dy(BPh<sub>4</sub>) (Fig. 2). An immediate colour change to dark red was observed, which gradually turned to a lighter red while stirring over the course of 1 h. After 16 h of reaction time, first workup of the mixture and then crystallisation followed from a hot concentrated toluene solution, allowing isolation of [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-tan)] (**1**) as dark red crystals in 41% yield.

**1** constitutes the first crystallographic evidence of a tan<sup>2-</sup>-containing complex and simultaneously the first introduction of tan into rare earth metal chemistry. **1** can be crystallised from various solvents, including concentrated DCM or THF solutions, however, hot toluene crystallisations gave reproducibly the highest yields.

Complex **1** comprises two dysprosium(III) ions, each η<sup>5</sup>-ligated by two Cp\* ligands, and a tetradentate tan<sup>2-</sup>-ligand that is coordinated to both metal centres slightly asymmetrically through two nitrogen atoms on each site, ultimately acting as a bridge (Fig. 2). The asymmetric unit of **1** consists of one dysprosocenium moiety ligated by half a tan<sup>2-</sup> unit due to a molecule-inherent inversion centre. The intramolecular Dy...Dy distance of 6.978(1) Å is considerably shorter than the closest intermolecular Dy...Dy distance of 8.477(1) Å (Table 1). A comparison of the intra-tan<sup>2-</sup> distances to our 2,2'-





Fig. 2 Synthesis of  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan})]$  (**1**) via salt metathesis of  $\text{Cp}^*_2\text{Dy}(\text{BPh}_4)$  with  $\text{K}_2\text{tan}$  (left). Structure of the  $\text{tan}^{2-}$  bridged complex **1**, obtained through single-crystal X-ray diffraction analysis (right). Green, blue, and grey spheres represent dysprosium, nitrogen, and carbon atoms, respectively. All hydrogen atoms and solvent molecules are omitted for clarity.

Table 1 Selected interatomic distances (Å) and angles (deg) of the tan-bridged Dy complexes,  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan})]$  (**1**) and  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan}^{\cdot})][\text{BARF}_{20}]$  (**2**)

	<b>1</b>	<b>2 (M1)<sup>a</sup></b>	<b>2 (M2)<sup>b</sup></b>
Tan oxidation state	2-	1-	1-
Dy-N	2.377(2); 2.365(2)	2.445(3); 2.436(3)	2.448(4); 2.453(4)
Dy-C (central)	2.771(3)	2.852(3)	2.878(4)
C-C (central)	1.443(6)	1.436(6)	1.411(7)
Dy...Dy	6.978(1)	7.139(1)	7.165(1)
Dy-C (avg.)	2.650(8); 2.656(11)	2.629(3)	2.644(7); 2.611(8)
Cnt <sup>c</sup> -Dy	2.406; 2.325	2.333; 2.335	2.335; 2.327
	2.388; 2.334		2.374; 2.297
Cnt-Cnt <sub>PhF5</sub> <sup>d</sup>	—	4.047	—
Cnt-Cnt <sup>e</sup>	—	—	4.394; 4.077
Cnt-Dy-Cnt	143.9; 139.5	143.9	144.2; 144.2
Dy-N-N'-Dy'	26.4(4)	5.2(5)	7.3(7)
Pz <sub>plane1</sub> -Pz <sub>plane2</sub> <sup>f</sup>	0.1(1)	0.1(1)	0.1(1)
tan <sub>plane</sub> -tan <sub>plane</sub> <sup>g</sup>	84.8(1)		7.4(2)
tan <sub>line</sub> -tan <sub>line</sub> <sup>h</sup>	84.8		48.1

<sup>a</sup> Edge-centred molecule. <sup>b</sup> Face-centred molecule. <sup>c</sup> Cnt = centroid of the pentamethylcyclopentadienyl ring. <sup>d</sup> Distance between adjacent Cp\* and BARF centroids. <sup>e</sup> Distance between adjacent Cp\* centroids. <sup>f</sup> Intramolecular angle between pyrazine (pyz) rings. <sup>g</sup> Intermolecular angle between tan planes. <sup>h</sup> Intermolecular angle between lines bisecting the tan ligands.

bisbenzimidazole (Bbim) bridged dysprosium complex<sup>42</sup> offers an appealing opportunity to assess the structural impact of different bridging ligands.

Comparing **1** to  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-Bbim})]$ , the central C-C bond of the tan ligand is almost identical with 1.443(6) Å (deviation  $\Delta = 0.012$  Å).<sup>18</sup> The average metal-nitrogen distance is considerably contracted by 0.052 Å from 2.423(4) Å in the Bbim complex to 2.371(3) Å in **1**. Most prominently, the Dy...Dy distance is substantially contracted by 0.775 Å in **1**, which stems from reduced steric demand of the tan *versus* the Bbim ligand. This also gives rise to a more pronounced out-of-plane displacement of the Dy centres *versus* the bridging ligand as suggested by the larger Dy-N-N'-Dy' angle of 26.4(4)° in **1** relative to 11.8(3)° in  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-Bbim})]$ .

Cyclic voltammetry experiments hinted at the electrochemical accessibility of the  $\text{tan}^{1-\cdot}$  oxidation state (see below), which prompted the synthesis of the  $\text{tan}^{1-\cdot}$  radical-bridged Dy complex  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan}^{\cdot})]^+$  (**2**) via chemical oxidation of **1**. A DCM solution of **1** was exposed to the oxidant thianthrenium tetrakis(pentafluorophenyl)borate  $[\text{Thian}^{\cdot}][\text{BARF}_{20}]$  affording a rapid colour change from intense red to black, indicative of

the formation of a  $\text{tan}^{1-\cdot}$  radical-containing compound (Fig. 4). **2** was crystallised from *n*-hexane layering of a concentrated DCM solution at -35 °C as black blocks in 79% yield over three days. Excitingly, **2** constitutes the first example of a crystallographically characterised coordination complex bearing a tan radical.

SCXRD analysis of **2** confirmed the topological retention of the tan-bridged complex after oxidation and the presence of the  $[\text{BARF}_{20}]^-$  counter anion in the crystal lattice which proves electron transfer onto the cationic metal complex indicating an oxidation state change of the bridging tan ligand (Fig. 4). This is reflected in the elongation of the Dy-N distances by ~0.08 Å and in the Dy...Dy distances by 0.16–0.19 Å, in accordance with a smaller charge of the tan bridge in **2**. Similar to **1**, the Dy-N distances in **2** are slightly asymmetric (Table 1). Relative to the bpym<sup>1-\cdot</sup>-containing Dy complex  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-bpym}^{\cdot})][\text{BPh}_4]$  (bpym = 2,2'-bipyrimidine), these distances are slightly elongated with an average Dy-N distance of 2.42(1) Å compared to 2.446(4) Å in **2**.<sup>24</sup> The average Dy...Dy distance is significantly longer by  $\Delta = 0.727$  Å relative to the bpym<sup>1-\cdot</sup>-containing Dy complex, which correlates with a decreased Dy-N-N'-Dy' angle by 10.6° due to reduced steric demand of the smaller tan ligand







Fig. 3 Cyclic voltammograms of  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan})]$  (1) (A) and  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan}')][\text{BARF}_{20}]$  (2) (B), measured in DCM at 300 K with  $0.22 \text{ mmol L}^{-1}$   $[\text{t}^+\text{Bu}_4\text{N}][\text{PF}_6]$  supporting electrolyte and  $3 \text{ mmol L}^{-1}$  analyte concentration against a Ag wire pseudo reference electrode with a  $100 \text{ mV s}^{-1}$  scan rate.

Compared to our reference complex  $[(\text{Cp}^*_2\text{Y})_2(\mu\text{-flv}')][\text{Al}(\text{OC}(\text{CF}_3)_3)_4]$ , the  $E_{1/2}$  for the  $\text{flv}^{1-}/\text{flv}^{2-}$  process appears at  $-0.935(2) \text{ V}$  (versus  $\text{Fc}^+/\text{Fc}$  in difluorobenzene), which is significantly shifted by  $0.285 \text{ V}$  towards negative potentials compared

to 2.<sup>42</sup> At first glance, this is counterintuitive as in linear azaacenes, the HOMO and LUMO energies strongly hinge on the number of rings and substituents in the molecule.

Namely the LUMO energy declines with rising number of rings, while the HOMO energy increases resulting in a net decrease in the HOMO–LUMO gap through the ring addition.<sup>84,85</sup> Likewise, chemical substitution with electron-accepting groups is expected to shrink the HOMO–LUMO gap.<sup>86</sup> However, these trends have been established considering closed-shell azaacenes, and reduced open-shell molecules are largely unexplored, let alone when bound to metal ions. In a rare case study, we discovered that both the HOMO–LUMO gap and  $\text{flv}^{1-}/\text{flv}^{2-}$  redox potential of the free  $\text{flv}^{1-}$  radical shrink upon coordination to Lewis-acidic yttrium ions.<sup>42</sup> Hence, the net decrease in  $E_{1/2}$  observed for 2 vs. the  $\text{flv}^{1-}$  reference complex probably originates from a combination of compensatory influences due to the formal contraction of the flv ligand by two Ph rings and double dysprosium coordination.

Recently, some of us reported the electrochemical properties of the free  $\text{tan}^{1-}$  radical in the form of  $[\text{K}(\text{crypt-222})][\text{tan}^{\cdot-}]$  and  $[\text{K}(18\text{-c-6})][\text{tan}^{\cdot-}]$ .<sup>47</sup> For  $[\text{K}(\text{crypt-222})][\text{tan}^{\cdot-}]$ , one quasi-reversible feature corresponding to the  $\text{tan}^{1-}/\text{tan}^{2-}$  process was found at  $-1.96 \text{ V}$ , and a second quasi-reversible feature for the  $\text{tan}^0/\text{tan}^{1-}$  process was observed at  $-1.04 \text{ V}$  (versus  $\text{Fc}^+/\text{Fc}$ ). Compared to  $[\text{K}(\text{crypt-222})]\text{flv}'$ , the  $E_{1/2}$  for the  $\text{flv}^{1-}/\text{flv}^{2-}$  ( $-1.608(3) \text{ V}$ ) and the  $\text{flv}^0/\text{flv}^{1-}$  processes ( $-0.902(4) \text{ V}$ ) are considerably shifted towards negative potentials due to formal removal of the peripheral Ph rings from flv.<sup>42</sup>

### Static magnetic susceptibility measurements

The magnetic exchange coupling between the  $\text{Dy}^{\text{III}}$  ions and the  $\text{tan}^{1-}$  radical-bridge was first canvassed through the measurement of the temperature dependence of the product of magnetic susceptibility and temperature ( $\chi_{\text{M}}T$  vs.  $T$ ). Measurements were carried out on a polycrystalline sample of 2 at 0.1 T and 1.0 T applied direct current (dc) fields between 2 and 300 K (Fig. 6 and S12). In the following, the data collected under a 0.1 T applied dc field will be discussed. The acquired data under a 1.0 T field is available in the SI.

At 300 K, the  $\chi_{\text{M}}T$  value of  $29.12 \text{ cm}^3 \text{ K mol}^{-1}$  is in good agreement with the expected value of  $28.71 \text{ cm}^3 \text{ K mol}^{-1}$  for two magnetically isolated  $\text{Dy}^{\text{III}}$  ions ( $J = 15/2$  and  $g_J = 4/3$ ) and a radical spin ( $S = \frac{1}{2}$  and  $g = 2.00$ ). As the temperature is



Fig. 4 Synthesis of  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan}')][\text{BARF}_{20}]$  (2) through oxidation of  $[(\text{Cp}^*_2\text{Dy})_2(\mu\text{-tan})]$  (1) with  $[\text{Thian}^{\cdot+}][\text{BARF}_{20}]$  (left). Structure of 2, obtained through single-crystal X-ray diffraction analysis (right). Green, blue, and grey spheres represent dysprosium, nitrogen, and carbon atoms, respectively. All hydrogen atoms and the counter ion  $[\text{BARF}_{20}]^-$  are omitted for clarity.



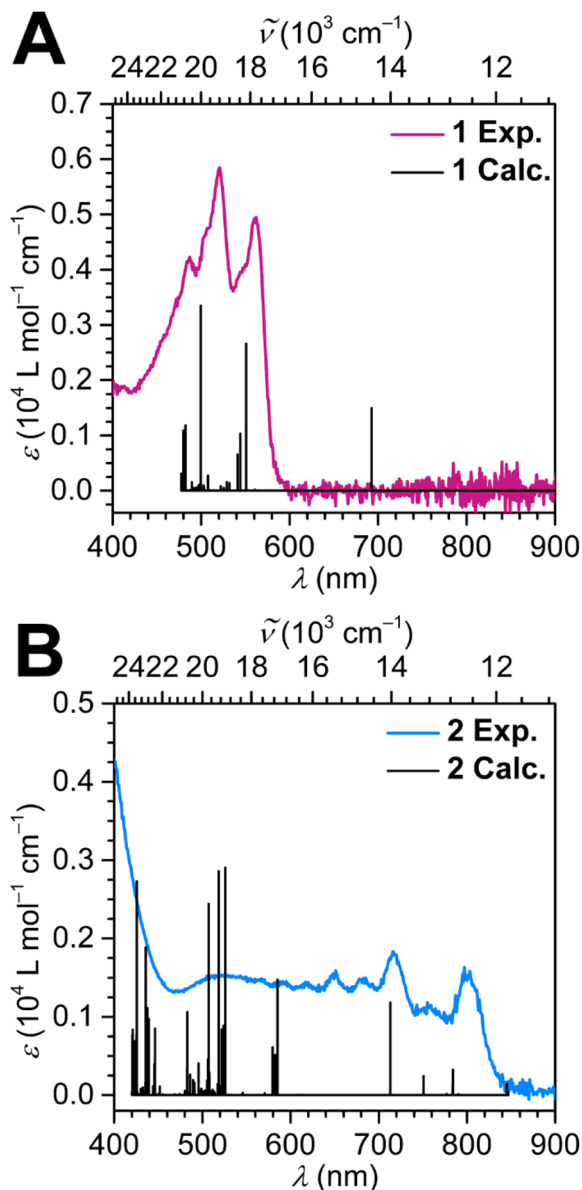


Fig. 5 UV-vis spectra of (A)  $[(\text{Cp}^*\text{Dy})_2(\mu\text{-tan})]$  (1) (pink line), and of (B)  $[(\text{Cp}^*\text{Dy})_2(\mu\text{-tan})][\text{BARF}_{20}]$  (2) (blue line), recorded at  $32 \mu\text{mol L}^{-1}$  (1) and  $140 \mu\text{mol L}^{-1}$  (2) concentrations in DCM at room temperature. Black vertical lines represent calculated TD-DFT transitions.

lowered, the  $\chi_{\text{M}}T$  product gradually declines to a minimum value of  $28.31 \text{ cm}^3 \text{ K mol}^{-1}$  at 95 K. With further decreasing temperature, a pronounced rise in  $\chi_{\text{M}}T$  occurs culminating in

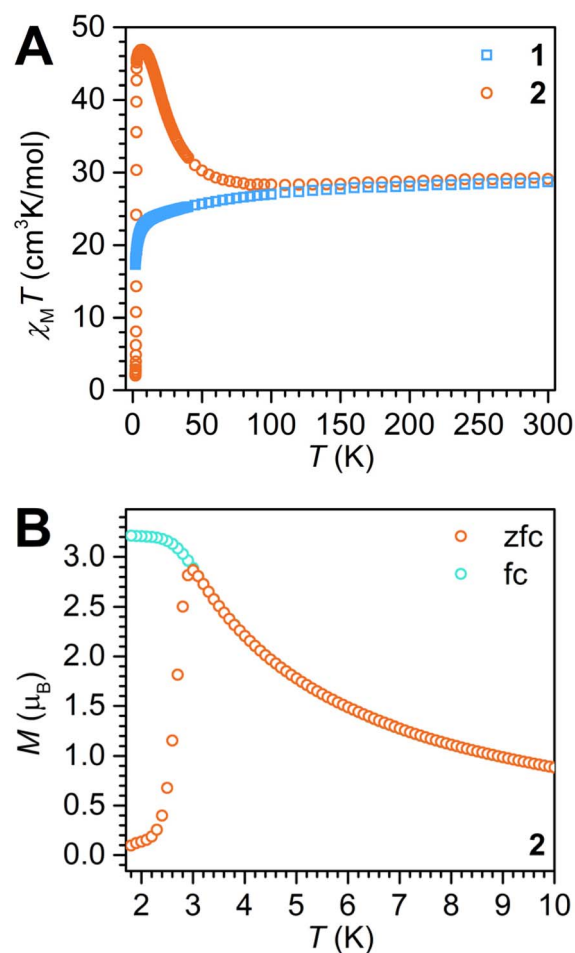


Fig. 6 (A) Variable-temperature dc magnetic susceptibility data for restrained polycrystalline samples of 1 (blue squares) and 2 (orange circles), respectively, collected under a 0.1 T applied dc field. (B) Plot of magnetisation vs. temperature for 2 during field-cooled (turquoise circles) and zero-field-cooled (orange circles) measurements displaying the thermoremanent magnetisation. 1.0 T data are displayed in Fig. S12 and S13.

a maximum value of  $46.88 \text{ cm}^3 \text{ K mol}^{-1}$  at 7 K, before displaying a steep drop to  $2.03 \text{ cm}^3 \text{ K mol}^{-1}$  at 2 K.

The progression of  $\chi_{\text{M}}T$  vs.  $T$ , in particular the occurrence of a shallow minimum at 95 K in  $\chi_{\text{M}}T$ , and the pronounced maximum reached at 7 K, suggests the presence of strong antiferromagnetic coupling between the  $\text{tan}^{1-}$  radical and the  $\text{Dy}^{\text{III}}$  centres, giving rise to the formation of a high-angular momentum. The steep drop at the lowest temperatures is

Table 2 Redox potentials of compounds containing  $\text{flv}^{1-}$  and  $\text{tan}^{1-}$  ligands versus the  $\text{Fc}^+/\text{Fc}^0$  couple

Compound	$E_{1/2}$ (1) (V) $\text{L}^0/\text{L}^{1-}$	$E_{1/2}$ (2) (V) $\text{L}^{1-}/\text{L}^{2-}$	Reference
$[\text{K}(\text{crypt-222})][\text{flv}^{\cdot-}]$	-0.902(4)	-1.608(3)	42
$[\text{K}(\text{crypt-222})][\text{tan}^{\cdot-}]$	-1.04	-1.96	47
$[(\text{Cp}^*\text{Y})_2(\mu\text{-flv}^{\cdot-})][\text{Al}(\text{OC}(\text{CF}_3)_3)_4]$	—	-0.935(2)	42
$[(\text{Cp}^*\text{Dy})_2(\mu\text{-tan}^{\cdot-})][\text{BARF}_{20}]$ (2)	—	-0.65(2)	This work
$[(\text{Cp}^*\text{Dy})_2(\mu\text{-tppz}^{\cdot-})][\text{BPh}_4]$	-0.64	-1.36	16



attributed to magnetic blocking which refers to a situation where the orientation of the magnetic moment is pinned by the strong magnetic anisotropy, rendering it incapable to follow the external field. This is further corroborated by the sharp divergence of zero-field-cooled (zfc) and field-cooled (fc)  $\chi_M T$  data at 3 K. A magnetic blocking event is exciting as it implies that at those temperatures the molecule could retain information.

Dc magnetic susceptibility measurements were also taken on a polycrystalline sample of **1** under 0.1 T and 1.0 T (Fig. 6 and S12). Under 0.1 T and 300 K, the  $\chi_M T$  value is  $28.67 \text{ cm}^3 \text{ K mol}^{-1}$  which is in good accordance with the anticipated value of  $28.33 \text{ cm}^3 \text{ K mol}^{-1}$  for two magnetically uncoupled  $\text{Dy}^{\text{III}}$  ions. Upon lowering the temperature,  $\chi_M T$  gradually decreases until  $\sim 17 \text{ K}$ , after which a more significant downturn occurs which is ascribed to thermal depopulation of low-lying excited states and/or antiferromagnetic coupling. Relative to **2**, magnetic blocking features are absent, as expected.

### Dynamic magnetic susceptibility measurements

The step drop in  $\chi_M T$  at low temperatures, and the divergence in zfc-/fc-cooled data revealed the presence of magnetic blocking in

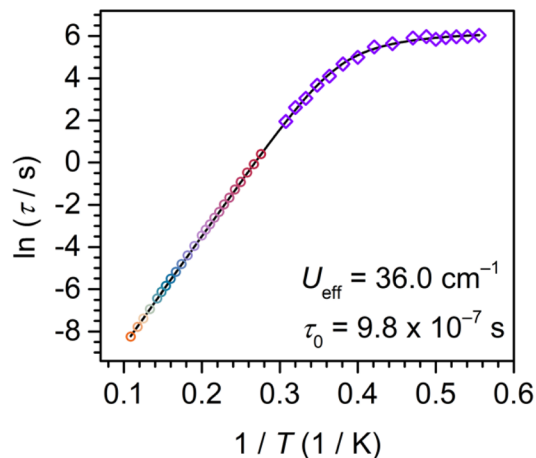


Fig. 8 Plot of natural log of the relaxation time *versus* the inverse temperature for **2** (temperature range 1.8 to 9.2 K). Red to orange circles represent data extracted from ac magnetic susceptibility measurements (temperature range 3.6 to 9.2 K), and purple diamonds represent data extracted from dc relaxation experiments (temperature range 1.8 to 3.25 K). The black line represents a fit to an Orbach, a Raman, and a quantum tunnelling process. Individual contributions of the multiple magnetic relaxation pathways are shown in Fig. S30.



Fig. 7 (A) Variable-temperature, variable-frequency in-phase ( $\chi_M'$ ) and (B) out-of-phase ( $\chi_M''$ ) ac magnetic susceptibility data collected under a zero Oe applied dc field for **2**, from 3.6 to 9.2 K. Solid lines indicate fits to the generalised Debye model.

**2**. To decipher the prevalent relaxation mechanisms, variable-frequency, variable-temperature in-phase ( $\chi_M'$ ) and out-of-phase ( $\chi_M''$ ) alternating current (ac) magnetic susceptibility measurements with an oscillating field of 3 Oe were conducted. Peaks were monitored in  $\chi_M''$  for **2**, suggestive of long magnetic relaxation times (Fig. 7). The extraction of magnetic relaxation times,  $\tau$ , proceeded through generating  $\chi_M''$  vs.  $\chi_M'$  plots for each temperature and fitting these Cole-Cole (Argand) plots to a generalised Debye function (Fig. S17). The relaxation times were employed in the construction of Arrhenius plots (Fig. 8, S29 and S30), where these allow the analysis of the temperature dependence of  $\tau$ , uncovering what type of magnetic relaxation pathways are operational. Specifically, the presence of an activation barrier in terms of moment reversal translates into the system needing to exchange energy with the lattice (as phonons) to climb to the pinnacle of the barrier before relaxation can set in. This type of a relaxation mechanism is known as an Orbach process,<sup>87,88</sup> and gives an exponential dependence of  $\tau$  upon temperature.

Specifically, subjecting **2** to ac frequencies of 0.1 to 1000 Hz at temperatures from 3.6 to 9.2 K, and under the absence of a dc field, the  $\chi_M''$  signal maximum changed frequency over the entire investigated temperature range. The relaxation times are fully temperature dependent over the entire temperature regime, suggesting an operative thermally activated relaxation process, which is reflected in the perfect linearity of the Arrhenius plot ( $\ln(\tau)$  vs.  $1/T$ ) (Fig. S19). A fit to the Arrhenius expression, namely a single Orbach process according to  $\tau^{-1} = \tau_0^{-1} \exp(-U_{\text{eff}}/k_B T)$ , afforded an effective energy barrier to spin relaxation  $U_{\text{eff}}$  of  $36.00(8) \text{ cm}^{-1}$  and attempt time  $\tau_0$  of  $9.8(2) \times 10^{-7} \text{ s}$  (Table 3). The low-temperature regime below 3.6 K is innate to very long relaxation times, and thus, is inaccessible through ac magnetic susceptibility methods. To gain insight



**Table 3** Best-fit parameters for the Arrhenius plots of **2** under a 0 Oe applied dc field

Temperature (K)	3.6–9.2	1.8–9.2 <sup>a</sup>	1.8–9.2 <sup>b</sup>
$U_{\text{eff}}$ (cm <sup>-1</sup> )	36.00(8)	36.2(1)	36.00
$\tau_0$ (s)	$9.8(2) \times 10^{-7}$	$1.00(5) \times 10^{-6}$	$9.8 \times 10^{-7}$
$C$ (s <sup>-1</sup> K <sup>-n</sup> )	—	$8(4) \times 10^{-7}$	$4(2) \times 10^{-6}$
$n$	—	8.9(4)	7.2(5)
$\tau_{\text{QTM}}$ (s)	—	447(10)	479(33)

<sup>a</sup> Orbach term freely refined. <sup>b</sup> Orbach parameters fixed to values derived from ac magnetic susceptibility data.



**Fig. 9** Plot of magnetisation (normalised) vs. time used to derive relaxation times for **2** at different temperatures from 1.8 to 3.25 K (inset: 2.38 to 3.25 K, shown separately for clarity). The temperatures were rounded to the second digit for improved readability. The data were fit (black line) to a function of the form  $M(t) = M_{\text{eq}} + (M_0 - M_{\text{eq}}) \exp(-(t/\tau)^\beta)$  where  $\beta$  is a stretch factor. Decay of the magnetisation vs. time for **2** was obtained by applying a magnetic field of 7 T to the sample at a given temperature for 5 min and then by quickly removing the magnetic field. The full data (unnormalised) recorded at each temperature are shown in Fig. S21–S28.

into the magnetisation dynamics at those low temperatures, dc magnetic relaxation experiments were carried out (Fig. 9). In this sophisticated technique, the sample is first magnetically saturated by the application of a high, 7 T dc field at high temperature, then cooled under field towards the temperature at which the measurement should take place. Second, after proper thermalisation, the dc field is quickly removed, and the time-dependent decay of the magnetisation is recorded. The relaxation will follow an exponential dependence. For **2**, dc relaxation experiments were performed between 1.80 and 3.25 K, and the relaxation times were obtained through fitting the decay curves to a stretched exponential function (Fig. S21–S28).

The relaxation times obtained from both dc relaxation experiments and ac magnetic susceptibility measurements were used to construct the Arrhenius plot in Fig. 8. Taking into account all relaxation times, a clear deviation from linearity is observed at low temperatures, pointing at additional relaxation pathways at play. A satisfactory fit to all  $\tau$  was ultimately attained by considering an Orbach, a Raman and a quantum tunnelling mechanism (QTM) according to eqn (2):

$$\tau^{-1} = \tau_0^{-1} \exp(-U_{\text{eff}}/k_{\text{B}}T) + CT^n + \tau_{\text{QTM}}^{-1} \quad (2)$$

where the first term corresponds to an Orbach process, the second term to a Raman process with  $C$  and  $n$  as the Raman coefficients, and the third term reflects the QTM process with  $\tau_{\text{QTM}}^{-1}$  as the QTM rate. Thus, the fit of all  $\tau$  yielded a spin-reversal barrier  $U_{\text{eff}}$  of 36.2(1) cm<sup>-1</sup> with a pre-exponential factor  $\tau_0$  of  $1.00(5) \times 10^{-6}$  s, Raman parameters of  $C = 8(4) \times 10^{-7}$  s<sup>-1</sup> K<sup>-n</sup> and  $n = 8.9(4)$ , and  $\tau_{\text{QTM}}$  of 447(10) s (Fig. S29 and Table 3). QTM typically impacts the low temperature regime, however, the magnitude of  $\tau_{\text{QTM}}$  implies the efficacy of Ln-radical coupling as a measure to attenuate QTM and thus, a slowdown of the magnetic relaxation. Notably, the  $n$  magnitude is rather large compared to other radical-bridged d-lanthanide SMMs. Thus, we probed the possibility of using the values obtained from ac measurements to reduce over parameterisation (Fig. S30). This alternate fit afforded  $C = 4(2) \times 10^{-6}$  s<sup>-1</sup> K<sup>-n</sup> and  $n = 7.2(5)$ , and  $\tau_{\text{QTM}}$  of 479(33) s which is more similar to values to other radical-bridged SMMs such as [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-dmeotz')(THF)][BPh<sub>4</sub>] with  $C = 9.62 \times 10^{-3}$  s<sup>-1</sup> K<sup>-n</sup> and  $n = 6.88$  or [K(thf)<sub>6</sub>][(Cp\*<sub>2</sub>Ln)<sub>2</sub>(μ-ind')] with  $C = 2.27 \times 10^{-3}$  s<sup>-1</sup> K<sup>-n</sup> and  $n = 8.2$  (dmeotz = 3,6-dimethoxy-1,2,4,5-tetrazine; ind = indigo).<sup>19,24,89</sup>

Taken together, the dynamic magnetic measurements provide evidence for the SMM behaviour of **2** with magnetic blocking occurring below 3.6 K.

For comparison, the dynamic magnetic behaviour for **1** was also explored (Fig. S15 and S16). Under frequencies ranging from 0.1 to 1000 Hz at temperatures from 5.5 to 21 K, the single  $\chi''$  peak changed frequency over the entire probed temperature range, suggestive of a thermally activated process.

The extracted relaxation times were fit to a Raman process, leading to an  $C = 3.3(5) \times 10^{-4}$  s<sup>-1</sup> K<sup>-n</sup> and  $n = 5.34(6)$  (Fig. S18). The additional inclusion of an Orbach process did not afford a satisfactory fit.

### Field-dependent magnetisation measurements

The employment of SMMs in storage applications requires a non-zero magnetisation under zero applied field. To probe the utility of **2** to this end, variable-field magnetisation measurements on a polycrystalline sample were carried out between  $\pm 7$  T and from 1.8 to 3.75 K with an average sweep rate of 0.01 T s<sup>-1</sup> (Fig. 10 and S33). The collected hysteresis loops are open below 3.75 K with a maximum coercive field  $H_{\text{C}}$  of 1.373 T at 1.8 K. This represents the highest  $H_{\text{C}}$  value found for any organic radical-bridged dinuclear SMM reported to date, where  $H_{\text{C}}$  has been at least doubled to tripled when compared to reported systems, taking into account conventional and somewhat akin sweep rates (Table 4):  $H_{\text{C}}$  is 0.6 T in [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-bpym')][BPh<sub>4</sub>], 0.54 T in [K(crypt-222)][(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-Bbim')], 0.5 T in [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-pyz')(THF)<sub>2</sub>][BPh<sub>4</sub>], and 0.6 T in [(Cp\*<sub>2</sub>Dy)<sub>2</sub>(μ-dmtz')(THF)<sub>2</sub>][BPh<sub>4</sub>] (bpym = bipyrimidine, Bbim = 2,2'-bisbenzimidazole, pyz = pyrazine, dmtz = 3,6-dimethyl-1,2,4,5-tetrazine).<sup>21,24,89</sup> Remarkably, the  $H_{\text{C}}$  value of **2** exceeds even that of SMMs that bear an inorganic radical, most notably an N<sub>2</sub><sup>3-</sup>, such as in [K(crypt-222)][(Cp<sup>Me,H</sup><sub>2</sub>Dy)<sub>2</sub>(μ-N<sub>2</sub>')] with an  $H_{\text{C}}$  of 1 T at 2 K ( $H_{\text{C}}$  is also 1 T at 5.5 K).<sup>90</sup>





Fig. 10 Plot of magnetisation ( $M$ ) vs. dc magnetic field ( $H$ ) at an average sweep rate of  $0.01 \text{ T s}^{-1}$  for 2: (A) from 1.8 to 3.75 K, and (B) at 1.8 K. (C) Plot of coercive field vs. temperature for 2, where solid line is a guide for the eye.

With rising temperatures in the variable-field magnetisation measurements of 2,  $H_c$  gradually decreases to first 0.953 T at 2.5 K, and then rapidly to 0.026 T at 3.5 K. Above the latter temperature,  $H_c$  further decreases and approaches the scan rate. Relative to the literature examples above, the hysteresis loops in 2 close at lower temperatures than for the bpym' (6.5 K), Bbim' (5.5 K) and pyz' (8 K) radical-bridged complexes, but close at a slightly higher temperature than the loops for the dmtz' complex (3.4 K).<sup>21,89</sup>

The hysteresis loops of 2 exhibit a prominent step at  $H = 0$  T, hinting at ground state quantum tunnelling of the magnetisation. This is in line with the pronounced curvature of the Arrhenius plot below 3.25 K, Fig. 8.

Noteworthy, analogous variable-field magnetisation measurements conducted for 1 using the same sweep rate, produced hysteresis loops from 1.8 to 5 K, Fig. S31, which visual appearance is vastly different relative to 2. In fact, the loops are barely open, with the coercive field reading only 590 Oe at 1.8 K. The pronounced quantum tunnelling in 1 on the timescale of the hysteresis measurements, is attributed to the presence of two noninteracting  $\text{Dy}^{\text{III}}$  ions. The result also demonstrates the power of implementing a radical as an exchange medium in between lanthanide ions, such as in 2, to afford magnetic memory effect.

Isothermal field-dependent magnetisation measurements ( $M$  vs.  $H$ ) for 2 were performed between 0 and 7 T and from 2 to 10 K (Fig. S35). At 2 K, the magnetisation curve exhibits a pronounced S-shape, associated with large magnetic anisotropy and magnetic blocking. Under an applied external magnetic field,  $M$  first raises to  $0.17\mu_B$  at 0.126 T, then plateaus at  $\sim 0.700$  T, before rapidly boosting to  $10.07\mu_B$  at  $\sim 2.480$  T. Subsequently, the ascent of  $M$  is slower until the maximum  $M_{\text{max}}$  value of  $10.99\mu_B$  at 7 T, albeit not reaching full magnetic saturation. This  $M_{\text{max}}$  is in excellent agreement with other radical-bridged dinuclear complexes such as  $10.97\mu_B$  for  $[\text{K}(\text{thf})_6][(\text{Cp}^*_2\text{Dy})_2(\mu\text{-ind}')] \cdot \text{THF}$  (where ind = indigo) and  $11.25\mu_B$  for  $[\text{K}(\text{crypt-222})][(\text{Cp}^*_2\text{Dy})_2(\mu\text{-Bbim}')]$ , respectively.<sup>18,19</sup> At higher temperatures, the S-shape disappears, and the  $M$  vs.  $H$  curves exhibit a continuous shape akin to paramagnetic compounds with negligible magnetic anisotropy. The reduced magnetisation curves ( $H/T$  vs.  $M$ ) are non-superimposable at low temperatures but increasingly overlap at 6 K and above (Fig. S35). This is yet another indication for low-lying excited states originating from magnetic coupling between  $\text{Dy}^{\text{III}}$  and radical centres and/or crystal field splitting.

The occurrence of such a large coercive field while simultaneously possessing a modest hysteresis temperature appears counterintuitive at first, as one would assume a correlation of the two parameters. Although extremely rare, such observations were made for larger systems containing four metals such as  $[(\text{Cp}^*_2\text{Dy})_4(\mu\text{-pyz}')_4] \cdot 10\text{THF}$  with an  $H_c$  of 6.5 T, where the hysteresis closes at 9 K, which is on par with dinuclear systems.<sup>21</sup> Other multimetallic comparative examples include  $[(\text{Cp}^*_2\text{Dy})_3(\mu_3\text{-HAN}')] \cdot \text{THF}$  (HAN = hexaazatrinaphthylene) with  $H_c = 0.8$  T and open hysteresis loops below 3.5 K.<sup>17</sup>

Considering the canvassed bridging ligands and coordination geometries so far, there is no trend in the magnitude of  $H_c$  and hysteresis temperature detectable. This underlines the importance of exploring new radical systems accompanied by magneto-structural correlations towards a substantial improvement in performance of polynuclear lanthanide SMMs.

#### Cauchy probability distribution function (CPDF) analysis

Cauchy probability distribution function (CPDF) analysis<sup>91</sup> was carried out on the reverse sweep of the magnetic hysteresis data

**Table 4** Selected examples of dinuclear radical-bridged dysprosium SMMs with coercive field ( $H_C$ ), hysteresis temperature ( $T_H$ ) and magnetic exchange coupling ( $J$ )

Compound	$H_C$ (T)	$T_H^a$ (K)	$J$ (cm $^{-1}$ )	Reference
$[(Cp^*_2Dy)_2(\mu-bpym')][BPh_4]$	0.6	6.5	$-10.0^b$	24
$[K(crypt-222)][(Cp^*_2Dy)_2(\mu-Bbim')]$	0.54	5.5	$-1.96^b$	18
$[(Cp^*_2Dy)_2(\mu-tppz')][BPh_4]$	0.1	3.25	$-6.91(4)^b$	16
$[(Cp^*_2Dy)_2(\mu-pyz')(THF)_2][BPh_4]$	0.5	8	$-22.2^b$	21
$[(Cp^*_2Dy)_2(\mu-dmtz')(THF)_2][BPh_4]$	0.6	3.4	$-11.7^b$	89
$[K(crypt-222)][(Cp^{Me,H}_2Dy)_2(\mu-N_2')]$	1	8	$-20.0^b$	90
$[(Cp^*_2Dy)_2(\mu-tan')][BARF_{20}](2)$	1.373	3.75	$\sim -24^c$	This work

<sup>a</sup> Signifies open magnetic hysteresis loops at or below this temperature. <sup>b</sup> Determined from fitting of the dc susceptibility data of the corresponding Gd complexes. <sup>c</sup> Determined from broken-symmetry DFT calculations. Abbreviations: bpym = 2,2'-bipyrimidine, Bbim = 2,2'-bisbenzimidazole, tppz = 2,3,5,6-tetra(2-pyridyl)pyrazine, pyz = pyrazine, dmtz = 3,6-dimethyl-1,2,4,5-tetrazine, tan = 1,4,5,8-tetraazanaphthalene. Employed sweep rates were conventional and varied between 20 and 100 Oe for the selected examples.



**Fig. 11** (A) First derivative of the reverse sweep of the magnetic hysteresis loop of **2** at 1.8 K is shown with a dashed line. P1, P2 and P5 are distinct demagnetisation processes uncovered through the Cauchy probability distribution function analysis. P3 and P4 processes are not observed at temperatures below 2.25 K. (B) First derivatives of the reverse sweep of the magnetic hysteresis loops of **2** collected from 1.8 K to 3.75 K.

of **2** to unveil traceable demagnetisation processes. A magnetic hysteresis loop can be reproduced through a summation of arctangent functions.<sup>92</sup> The magnetic hysteresis loop data of **2** from 1.8 K to 3.75 K were fit using arctangent functions and the first derivative of each fit was attained, Fig. 11. The inflection points in the first derivative correspond to different demagnetisation processes that are buried within the magnetic hysteresis data. Since the first derivative of an arctangent function follows a Lorentzian distribution, it can be analysed using CPDF. This analysis provides information about the half-width at half maximum ( $\gamma$ ), the field position, and the peak amplitude for each demagnetisation process.

Five different demagnetisation events (P1, P2, P3, P4 and P5) are observed for the hysteresis data of **2** from 1.8 K to 3.75 K, Fig. 11. Out of these, P1 is the only process observed throughout the entire temperature regime. P1 is mainly located at  $\sim 0$  T field and is very narrow ( $\gamma \sim 0.02$  T) up until 2.5 K (Table S3). As the temperature increases, P1 becomes broader ( $\gamma \sim 0.2$  T) and shifts towards positive field positions (0.12 T) at 3.75 K. Due to the narrowness and its position at 0 T, P1 is attributed to a QTM process contributing to magnetic relaxation. With increasing temperature, the percent contribution of P1 remains constant until 2.5 K (Fig. S37). Above this temperature, the percent contribution fluctuates. Since the P1 peak broadens and features temperature-dependent behaviour above 2.5 K, it can be deduced that at higher temperatures P1 does not constitute of a pure QTM process and thermally activated relaxation processes are coalescing to produce a unified demagnetisation process.

P2 is a broader process occurring at around  $-1.26$  T at 1.8 K, which gradually shifts towards more positive field values. Beyond 2.25 K, P2 disappears, and two new processes (P3 and P4) originate. These are also broad, and they shift toward positive field values with higher temperatures (Fig. S36 and Table S3). P3 appears at 2.5 K and exhibits an upward trend in percent contribution until 3.75 K and P4 is only observed at temperatures from 2.5 K to 3.0 K. P5 is the demagnetisation process that occurs at the most negative field position of  $-1.69$  T at 1.8 K and also gradually moves towards positive field values with rising temperature. The percent contribution from P5



gradually declines with increasing temperatures and reaches zero at 3.25 K, beyond which it is not observable.

In sum, the evaluation of the magnetic hysteresis data by means of CPDF, points at different processes contributing towards the demagnetisation of **2**. At low temperatures, a QTM process is clearly identified at approximately 0 T field, whereas raising the temperature induces the origination of additional demagnetisation processes owing to thermally activated relaxation processes. At high temperatures, pure QTM processes are not observed, and different demagnetisation processes coalesce resulting in two processes.

### Derivation of magnetic coupling from density functional theory

The multiconfigurational nature of Dy<sup>III</sup> ions renders commonly employed fitting methods of  $\chi_{MT}$  vs.  $T$  data as tools to derive magnetic coupling constants,  $J$ , inaccessible as the required crystal field parameters are usually unknown.

Computational methods such as broken-symmetry density functional theory are useful to derive  $J$  for isotropic systems such as Gd<sup>III</sup> ions and organic radicals.<sup>93</sup> Hence, the coupling in **2** can be approximated by calculating model complexes, **2**<sup>Gd</sup>, with Dy substituted for Gd, and subsequent scaling of the obtained values to account for the larger magnetic moment of Dy.

To analyse the intramolecular coupling in the different conformers of **2**, broken-symmetry DFT calculations were carried out on the atomic coordinates of **2** with Dy being substituted by Gd. These calculations were performed on the edge-centred molecular unit (M1) and the two disorder parts of the face-centred molecular unit (M2A and M2B). The exchange coupling constant ( $J$ ) was determined through the Heisenberg–Dirac–van Vleck spin Hamiltonian ( $\hat{H} = -2J \cdot S_{Dy} \cdot S_{Rad}$ ) and  $J$  was calculated by  $J = -(E_{HS} - E_{BS}) / (\langle S^2 \rangle_{HS} - \langle S^2 \rangle_{BS})$  formalism. Here,  $E_{HS}$  and  $E_{BS}$  are the energies of the high spin and the broken-symmetry states, respectively, and  $\langle S^2 \rangle_{HS}$  and  $\langle S^2 \rangle_{BS}$  represent the spin expectation values of the high spin and broken-symmetry states.<sup>93</sup>

As anticipated for an organic radical-bridged complex, the spin density primarily resides on the Gd centres and on the bridging tan ligand (Fig. S38 and Table S4). All three molecular units exhibit similar, huge antiferromagnetic exchange coupling as evidenced by the exchange coupling constant values ( $J_{Gd-rad}$ ) obtained through DFT. The  $J_{Gd-rad}$  values are  $-17.7 \text{ cm}^{-1}$ ,  $-16.6 \text{ cm}^{-1}$ , and  $-16.7 \text{ cm}^{-1}$  for M1, M2A, and M2B, respectively, confirming an approximately  $1 \text{ cm}^{-1}$  difference.

The derived magnetic exchange coupling constants hint at extremely strong coupling in **2**, even relative to other radical-bridged dinuclear Gd complexes such as  $J_{Gd-rad} = -10.8 \text{ cm}^{-1}$  obtained for  $[(Cp^*_2Gd)_2(\mu-5,5'-F_2bpym^*)][BPh_4]$ , or  $J_{Gd-rad} = -11.7 \text{ cm}^{-1}$  for  $[(Cp^*_2Gd)_2(\mu-dmtz^*)(THF)_2][BPh_4] \cdot THF$ .<sup>89,94</sup> The average  $-17.0 \text{ cm}^{-1}$  for **2**<sup>Gd</sup> is only surpassed by  $-22.2 \text{ cm}^{-1}$  determined for the pyrazinyl-bridged  $[(Cp^*_2Gd)_2(\mu-pyz^*)(THF)_2][BPh_4]$ ,<sup>21</sup> and highlights the immense potential of linear azaacenes to promote strong magnetic coupling.

The determined  $J_{Gd-rad}$  values for **2**<sup>Gd</sup> were rescaled to obtain the approximate  $J_{Dy-rad}$  value for the Dy complex **2**.  $J_{Dy-rad}$  can be attained by multiplying  $J_{Gd}$  by 1.4.<sup>15</sup> This results in  $J_{Dy-rad}$  values of  $\sim -25 \text{ cm}^{-1}$  for M1 and  $\sim -23 \text{ cm}^{-1}$  M2A, and M2B. These are DFT approximations of the real exchange coupling values, however, both sign and magnitude are in excellent agreement with the experimental finding of strong antiferromagnetic coupling, giving rise to a “giant spin” state and accompanied magnetic blocking.

## Conclusions

The dianionic ligand 1,4,5,8-tetraazaphthalene (tan) was used to generate the first dinuclear lanthanide complex containing the  $\text{tan}^{2-}$  bridging ligand,  $[(Cp^*_2Dy)_2(\mu-tan)]$  (**1**). Complex **1** was chemically oxidised to yield  $[(Cp^*_2Dy)_2(\mu-tan^{\cdot-})][BarF_{20}]$  (**2**), consisting of the radical bridging ligand,  $\text{tan}^{1\cdot-}$ . Notably, complex **2** represents the first coordination compound containing a tan radical with any metal ion. Both **1** and **2** show slow magnetic relaxation under zero applied dc field. Specifically, the magnetic characterisation of **2** revealed that the  $\text{tan}^{1\cdot-}$  ligand promotes strong antiferromagnetic exchange coupling with the highly anisotropic dysprosium ions. The arising “giant-spin” leads to SMM behaviour with open hysteresis loops. In fact, a maximum coercive field of 1.373 T is observed which sets a record for organic radical-bridged dinuclear SMMs. The hysteresis loops are open below 3.75 K, thus exceeding most dinuclear SMMs reported to date. The magnetic exchange coupling strength was estimated *via* broken-symmetry DFT calculations, revealing a massive coupling of  $\sim -24 \text{ cm}^{-1}$ , ranging among the highest determined for radical-bridged lanthanide complexes.

These foregoing results demonstrate that rational chemical design of the bridging ligand to adjust the ligand's reduction potential to the high negative Dy<sup>III</sup>/Dy<sup>II</sup> redox potential pose an auspicious avenue for performance improvements of radical-bridged SMMs. The design of bridging ligands with L/L<sup>·-</sup> redox processes at even lower potentials are expected to drastically boost temperatures. Moreover, the construction of higher-nuclearity lanthanide-radical systems employing tan may amplify hard magnet properties further and lead to powerful magnetic materials.

## Author contributions

Florian Benner synthesised the complexes, conducted SCXRD, spectroscopy and magnetic measurements including interpretation. Saroshan Deshapriya conducted and interpreted TDDFT and broken-symmetry DFT calculations, and CPDF fits. Selvan Demir wrote the manuscript with the input from all authors, led the project and provided resources and support.

## Conflicts of interest

There are no conflicts to declare.



## Data availability

CCDC 2455536 (1) and 2455829 (2) contain the supplementary crystallographic data for this paper.<sup>95a,b</sup>

Supplementary information: all computational data, Python scripts for CPDF analysis, spectroscopic data, SI figures and tables, and detailed crystallographic information. See DOI: <https://doi.org/10.1039/d5sc05358g>.

## Acknowledgements

Selvan Demir is grateful to the Department of Chemistry at Michigan State University (MSU) for generous start-up funds and the National Science Foundation for Grant No. CHE-2339595 (CAREER). This work was supported in part through computational resources and services provided by the Institute for Cyber-Enabled Research at MSU.

## Notes and references

- D. Reinsel, J. Gantz and J. Rydning, Data Age 2025 – The Evolution of Data to Life-Critical, <https://www.seagate.com/files/www-content/our-story/trends/files/Seagate-WP-DataAge2025-March-2017.pdf>, (accessed 28 May 2025).
- S. Zoting and A. Shivarkar, AI Powered Storage Market Size, Share, and Trends 2025 to 2034, <https://www.precedenceresearch.com/ai-powered-storage-market>, (accessed 28 May 2025).
- K. H. J. Buschow and A. S. Van Der Goot, Intermetallic compounds in the system samarium-cobalt, *J. Less-Common Met.*, 1968, **14**, 323–328.
- H. R. Kirchmayr, Permanent magnets and hard magnetic materials, *J. Phys. D Appl. Phys.*, 1996, **29**, 2763–2778.
- J. F. Herbst, J. J. Croat, F. E. Pinkerton and W. B. Yelon, Relationships between crystal structure and magnetic properties in Nd<sub>2</sub>Fe<sub>14</sub>B, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1984, **29**, 4176–4178.
- E. Moreno-Pineda and W. Wernsdorfer, Measuring molecular magnets for quantum technologies, *Nat. Rev. Phys.*, 2021, **3**, 645–659.
- G. Gabarró-Riera and E. C. Sañudo, Challenges for exploiting nanomagnet properties on surfaces, *Commun. Chem.*, 2024, **7**, nwac194.
- J. D. Rinehart and J. R. Long, Exploiting single-ion anisotropy in the design of f-element single-molecule magnets, *Chem. Sci.*, 2011, **2**, 2078–2085.
- S. Gómez-Coca, D. Aravena, R. Morales and E. Ruiz, Large magnetic anisotropy in mononuclear metal complexes, *Coord. Chem. Rev.*, 2015, **289–290**, 379–392.
- C. A. Gould, K. R. McClain, D. Reta, J. G. C. Kragoskow, D. A. Marchiori, E. Lachman, E. Choi, J. G. Analytis, R. D. Britt, N. F. Chilton, B. G. Harvey and J. R. Long, Ultrahard magnetism from mixed-valence dilanthanide complexes with metal–metal bonding, *Science*, 2022, **375**, 198–202.
- S. Demir, I. R. Jeon, J. R. Long and T. D. Harris, Radical ligand-containing single-molecule magnets, *Coord. Chem. Rev.*, 2015, **289–290**, 149–176.
- Y.-C. Chen and M.-L. Tong, Single-Molecule Magnets beyond a Single Lanthanide Ion: The Art of Coupling, *Chem. Sci.*, 2022, **13**, 8716–8726.
- A. Swain and T. Sharma, Strategies to quench quantum tunneling of magnetization in lanthanide single molecule magnets, *Chem. Commun.*, 2023, **59**, 3206–3228.
- P. Zhang, R. Nabi, J. K. Staab, N. F. Chilton and S. Demir, Taming Super-Reduced Bi<sub>2</sub><sup>3+</sup> Radicals with Rare Earth Cations, *J. Am. Chem. Soc.*, 2023, **145**, 9152–9163.
- N. Mavragani, D. Errulat, D. A. Gálico, A. A. Kitos, A. Mansikkamäki and M. Murugesu, Radical Bridged Ln<sub>4</sub> Metallocene Complexes with Strong Magnetic Coupling and Large Coercive Field, *Angew. Chem., Int. Ed.*, 2021, **60**, 24206–24213.
- S. Demir, M. Nippe, M. I. Gonzalez and J. R. Long, Exchange coupling and magnetic blocking in dilanthanide complexes bridged by the multi-electron redox-active ligand 2,3,5,6-tetra(2-pyridyl)pyrazine, *Chem. Sci.*, 2014, **5**, 4701–4711.
- C. A. Gould, L. E. Darago, M. I. Gonzalez, S. Demir and J. R. Long, A Trinuclear Radical-Bridged Lanthanide Single-Molecule Magnet, *Angew. Chem., Int. Ed.*, 2017, **56**, 10103–10107.
- F. Benner, L. La Droite, O. Cador, B. Le Guennic and S. Demir, Magnetic Hysteresis and Large Coercivity in Bisbenzimidazole Radical-Bridged Dilanthanide Complexes, *Chem. Sci.*, 2023, **14**, 5577–5592.
- F.-S. Guo and R. A. Layfield, Strong direct exchange coupling and single-molecule magnetism in indigo-bridged lanthanide dimers, *Chem. Commun.*, 2017, **53**, 3130–3133.
- B. S. Dolinar, S. Gómez-Coca, D. I. Alexandropoulos and K. R. Dunbar, An air stable radical-bridged dysprosium single molecule magnet and its neutral counterpart: redox switching of magnetic relaxation dynamics, *Chem. Commun.*, 2017, **53**, 2283–2286.
- N. M. Neha Bajaj, A. A. Kitos, D. Chartrand, T. Maris, A. Mansikkamäki and M. Murugesu, Hard single-molecule magnet behavior and strong magnetic coupling in pyrazinyl radical-bridged lanthanide metallocenes, *Chem*, 2024, **10**, 2484–2499.
- P. Zhang, M. Perfetti, M. Kern, P. P. Hallmen, L. Ungur, S. Lenz, M. R. Ringenberg, W. Frey, H. Stoll, G. Rauhut and J. van Slageren, Exchange coupling and single molecule magnetism in redox-active tetraoxolene-bridged dilanthanide complexes, *Chem. Sci.*, 2018, **9**, 1221–1230.
- B. S. Dolinar, D. I. Alexandropoulos, K. R. Vignesh, T. James and K. R. Dunbar, Lanthanide Triangles Supported by Radical Bridging Ligands, *J. Am. Chem. Soc.*, 2018, **140**, 908–911.
- S. Demir, J. M. Zadrozny, M. Nippe and J. R. Long, Exchange Coupling and Magnetic Blocking in Bipyrimidyl Radical-Bridged Dilanthanide Complexes, *J. Am. Chem. Soc.*, 2012, **134**, 18546–18549.



- 25 F. Delano IV, E. Castellanos, J. McCracken and S. Demir, A rare earth metallocene containing a 2,2'-azopyridyl radical anion, *Chem. Sci.*, 2021, **12**, 15219–15228.
- 26 F. Benner and S. Demir, Isolation of the Elusive Bisbenzimidazole Bbim<sup>3-•</sup> Radical Anion and its Employment in a Metal Complex, *Chem. Sci.*, 2022, **13**, 5818–5829.
- 27 F. Delano and S. Demir, Implementation of 2,2'-azobispyridine radical mono- and dianions in dinuclear rare earth metal complexes, *Chem. Commun.*, 2024, **60**, 11702–11705.
- 28 G. David, N. Ferré and B. Le Guennic, Consistent Evaluation of Magnetic Exchange Couplings in Multicenter Compounds in KS-DFT: The Recomposition Method, *J. Chem. Theory Comput.*, 2023, **19**, 157–173.
- 29 G. David, G. Duplaix-Rata and B. Le Guennic, What governs magnetic exchange couplings in radical-bridged dinuclear complexes?, *Phys. Chem. Chem. Phys.*, 2024, **26**, 8952–8964.
- 30 W. W. Lukens, N. Magnani and C. H. Booth, Application of the Hubbard model to Cp\*<sub>2</sub>Yb(bipy), a model system for strong exchange coupling in lanthanide systems, *Inorg. Chem.*, 2012, **51**, 10105–10110.
- 31 M. T. Trinh, J. C. Wedal and W. J. Evans, Evaluating electrochemical accessibility of 4f<sup>n</sup>5d<sup>1</sup> and 4f<sup>n+1</sup> Ln(II) ions in (C<sub>5</sub>H<sub>4</sub>SiMe<sub>3</sub>)<sub>3</sub>Ln and (C<sub>5</sub>Me<sub>4</sub>H)<sub>3</sub>Ln complexes, *Dalton Trans.*, 2021, **50**, 14384–14389.
- 32 H. F. Li, P. F. Yan, P. Chen, Y. Wang, H. Xu and G. M. Li, Highly luminescent bis-diketone lanthanide complexes with triple-stranded dinuclear structure, *Dalton Trans.*, 2012, **41**, 900–907.
- 33 U. H. F. Bunz, J. U. Engelhart, B. D. Lindner and M. Schaffroth, Large N-heteroacenes: New tricks for very old dogs?, *Angew. Chem., Int. Ed.*, 2013, **52**, 3810–3821.
- 34 J. Li and Q. Zhang, Linearly Fused Azaacenes: Novel Approaches and New Applications beyond Field-Effect Transistors (FETs), *ACS Appl. Mater. Interfaces*, 2015, **7**, 28049–28062.
- 35 J. J. Bryant, Y. Zhang, B. D. Lindner, E. A. Davey, A. L. Appleton, X. Qian and U. H. F. Bunz, Alkynylated Phenazines: Synthesis, Characterization, and Metal-Binding Properties of Their Bis-Triazolyl Cycloadducts, *J. Org. Chem.*, 2012, **77**, 7479–7486.
- 36 J. Li, J. Gao, G. Li, W. Xiong and Q. Zhang, Azaisoquinolinones: N positions tell you different stories in their optical properties, *J. Org. Chem.*, 2013, **78**, 12760–12768.
- 37 C. Wang, G. Li and Q. Zhang, A novel heteroacene, 2-(2,3,4,5-tetrafluorophenyl)-1H-imidazo[4,5-b] phenazine as a multi-response sensor for F<sup>-</sup> detection, *Tetrahedron Lett.*, 2013, **54**, 2633–2636.
- 38 P. Y. Gu, Z. Wang and Q. Zhang, Azaacenes as active elements for sensing and bio applications, *J. Mater. Chem. B*, 2016, **4**, 7060–7074.
- 39 M. V. Mikhailenko, V. V. Ivanov, M. A. Faraonov, A. V. Kuzmin, S. S. Khasanov, I. A. Yakushev, N. N. Breslavskaya, E. N. Timokhina, T. Y. Astakhova, A. Otsuka, H. Yamochi, H. Kitagawa and D. V. Konarev, Effect of nuclearity and reduction state of the central ligand on magnetic properties of hexaazatrinaphthylene-based cobalt(II) and iron(II) complexes: From extremely weak to record-breaking antiferromagnetic exchange interaction, *Inorg. Chem.*, 2024, **11**, 7563–7575.
- 40 L. Barluzzi, S. P. Ogilvie, A. B. Dalton, P. Kaden, R. Gericke, A. Mansikkamäki, S. R. Giblin and R. A. Layfield, Triply Bonded Pancake  $\pi$ -Dimers Stabilized by Tetravalent Actinides, *J. Am. Chem. Soc.*, 2024, **146**, 4234–4241.
- 41 J. Gao and Q. Zhang, Understanding the electronic structure of larger azaacenes through DFT calculations, *Isr. J. Chem.*, 2014, **54**, 699–702.
- 42 F. Benner and S. Demir, Isolation of Elusive Fluoflavine Radicals in Two Differing Oxidation States, *J. Am. Chem. Soc.*, 2024, **146**, 26008–26023.
- 43 W. L. F. Armarego, Covalent Hydration in 1,4,5,8-Tetraazaphthalenes, *J. Chem. Soc.*, 1963, **824**, 4304–4312.
- 44 F. Gersonl and W. L. F. Armarego, ESR-Spektren des Radikal-Anions des 1,4,5,8-Tetraazaphthalin, *Helv. Chim. Acta*, 1965, **48**, 112–116.
- 45 R. Danieli, L. Lunazzi and G. Placucci, Tetraazaphthalene Radical Anions, *J. Am. Chem. Soc.*, 1971, **93**, 5850–5852.
- 46 G. F. Pedulli and M. Guerra, Radical Ion Pairs of 1,4,5,8-Tetraazaphthalen, *J. Magn. Reson.*, 1978, **32**, 243–249.
- 47 S. Deshapriya and S. Demir, Isolation of 1,4,5,8-Tetraazaphthalene Radicals, *Chem. Commun.*, 2025, **61**, 12301–12304.
- 48 W. J. Evans, S. A. Kozimor, J. W. Ziller and N. Kaltsoyannis, Structure, reactivity, and density functional theory analysis of the six-electron reductant, [(C<sub>5</sub>Me<sub>5</sub>)<sub>2</sub>U]<sub>2</sub>( $\mu$ - $\eta^6$ : $\eta^6$ -C<sub>6</sub>H<sub>6</sub>), synthesized via a new mode of (C<sub>5</sub>Me<sub>5</sub>)<sub>3</sub>M reactivity, *J. Am. Chem. Soc.*, 2004, **126**, 14533–14547.
- 49 B. J. Barker and P. G. Sears, Conductance Behavior of Some Ammonium and Partially Substituted Ammonium Tetraphenylborates in 3-Methyl-2-oxazolidone and 3-tert-Butyl-2-oxazolidone at 25°, *J. Phys. Chem.*, 1974, **78**, 2687–2688.
- 50 D. E. Bergbreiter and J. M. Killough, Reactions of Potassium-Graphite, *J. Am. Chem. Soc.*, 1978, **100**, 2126–2134.
- 51 A. L. Balch, R. C. Lechoslaw and M. M. Olmstead, Characterization of Five- and Six-Coordinate Iron (III) Complexes of IV-Methylporphyrins, *J. Am. Chem. Soc.*, 1990, **112**, 7552–7558.
- 52 W. S. E. Steckhan and W. Schmidt, Elektrochemische und spektroskopische Untersuchung bromsubstituierter Triarylamin-Redoxsysteme, *Chem. Ber.*, 1980, **113**, 577–585.
- 53 L. Dütsch, M. Fleischmann, S. Welsch, G. Balázs, W. Kremer and M. Scheer, Dicationic E<sub>4</sub> Chains (E = P, As, Sb, Bi) Embedded in the Coordination Sphere of Transition Metals, *Angew. Chem., Int. Ed.*, 2018, **57**, 3256–3261.
- 54 *CrysAlisPro Software system*, Rigaku Corporation, 2020.
- 55 SCALE3 ABSPACK, Empirical absorption correction, *CrysAlis Pro – Software Package*, Rigaku Corporation, 2020.
- 56 G. M. Sheldrick, SHELXT - Integrated space-group and crystal-structure determination, *Acta Crystallogr.*, 2015, **A71**, 3–8.



- 57 G. M. Sheldrick, Crystal structure refinement with SHELXL, *Acta Crystallogr.*, 2015, **C71**, 3–8.
- 58 O. V. Dolomanov, L. J. Bourhis, R. J. Gildea, J. A. K. Howard and H. Puschmann, OLEX2: A complete structure solution, refinement and analysis program, *J. Appl. Crystallogr.*, 2009, **42**, 339–341.
- 59 G. A. Bain and J. F. Berry, Diamagnetic Corrections and Pascal's Constants, *J. Chem. Educ.*, 2008, **85**, 532–536.
- 60 D. Reta and N. F. Chilton, Uncertainty estimates for magnetic relaxation times and magnetic relaxation parameters, *Phys. Chem. Chem. Phys.*, 2019, **21**, 23567–23575.
- 61 F. Weigend and R. Ahlrichs, Balanced basis sets of split valence, triple zeta valence and quadruple zeta valence quality for H to Rn: Design an assessment of accuracy, *Phys. Chem. Chem. Phys.*, 2005, **7**, 3297–3305.
- 62 M. Dolg, H. Stoll, A. Savin and H. Preuss, Energy-adjusted pseudopotentials for the rare earth elements, *Theor. Chim. Acta*, 1989, **75**, 173–194.
- 63 M. Dolg, H. Stoll and H. Preuss, A combination of quasirelativistic pseudopotential and ligand field calculations for lanthanoid compounds, *Theor. Chim. Acta*, 1993, **85**, 441–450.
- 64 J. Yang and M. Dolg, Valence basis sets for lanthanide 4f-in-core pseudopotentials adapted for crystal orbital *ab initio* calculations, *Theor. Chem. Acc.*, 2005, **113**, 212–224.
- 65 A. Weigand, X. Cao, J. Yang and M. Dolg, Quasirelativistic f-in-core pseudopotentials and core-polarization potentials for trivalent actinides and lanthanides: molecular test for trifluorides, *Theor. Chem. Acc.*, 2010, **126**, 117–127.
- 66 F. Weigend and R. Ahlrichs, Balanced basis sets of split valence, triple zeta valence and quadruple zeta valence quality for H to Rn: Design and assessment of accuracy, *Phys. Chem. Chem. Phys.*, 2005, **7**, 3297–3305.
- 67 D. Aravena, F. Neese and D. A. Pantazis, Improved Segmented All-Electron Relativistically Contracted Basis Sets for the Lanthanides, *J. Chem. Theory Comput.*, 2016, **12**, 1148–1156.
- 68 V. N. Staroverov, G. E. Scuseria, J. Tao and J. P. Perdew, Comparative assessment of a new nonempirical density functional: Molecules and hydrogen-bonded complexes, *J. Chem. Phys.*, 2003, **119**, 12129–12137.
- 69 V. N. Staroverov, G. E. Scuseria, J. Tao and J. P. Perdew, Erratum: Comparative assessment of a new nonempirical density functional: Molecules and hydrogen-bonded complexes, *J. Chem. Phys.*, 2004, **121**, 11507.
- 70 S. Grimme, J. Antony, S. Ehrlich and H. Krieg, Consistent and Accurate *Ab Initio* Parametrization of Density Functional Dispersion Correction (DFT-D) for the 94 Elements H–Pu, *J. Chem. Phys.*, 2010, **132**, 154104.
- 71 S. Grimme, S. Ehrlich and L. Goerigk, Effect of the damping function in dispersion corrected density functional theory, *J. Comput. Chem.*, 2011, **32**, 1456–1465.
- 72 F. Neese, The ORCA program system, *Wiley Interdiscip. Rev. Comput. Mol. Sci.*, 2012, **2**, 73–78.
- 73 F. Neese, Software update: The ORCA program system—Version 5.0, *Wiley Interdiscip. Rev. Comput. Mol. Sci.*, 2022, **12**, e1606.
- 74 F. Neese, The SHARK integral generation and digestion system, *J. Comput. Chem.*, 2023, **44**, 381–396.
- 75 J. D. Rolfe, F. Neese and D. A. Pantazis, All-electron scalar relativistic basis sets for the elements Rb–Xe, *J. Comput. Chem.*, 2020, **41**, 1842–1849.
- 76 W. Humphrey, A. Dalke and K. Schulten, VMD - Visual Molecular Dynamics, *J. Mol. Graph.*, 1996, **14**, 33–38.
- 77 P. J. N. Brown and E. F. Mooney, The infrared spectra of fluorinated aromatic compounds-I Methyl substituted 2,3,4,5,6-pentafluorodiphenyls, *Spectrochim. Acta, Part A*, 1968, **24**, 1317–1320.
- 78 A. G. Massey and A. J. Park, Perfluorophenyl derivatives of the elements. I. Tris(pentafluorophenyl)boron, *J. Organomet. Chem.*, 1964, **2**, 245–250.
- 79 F. Guo, B. M. Day, Y. Chen, M. Tong, A. Mansikkamäki and R. A. Layfield, Magnetic hysteresis up to 80 kelvin in a dysprosium metallocene single-molecule magnet, *Science*, 2018, **362**, 1400–1403.
- 80 C. A. P. Goodwin, F. Ortu, D. Reta, N. F. Chilton and D. P. Mills, Molecular magnetic hysteresis at 60 kelvin in dysprosocenium, *Nature*, 2017, **548**, 439–442.
- 81 C. A. P. Goodwin, D. Reta, F. Ortu, N. F. Chilton and D. P. Mills, Synthesis and Electronic Structures of Heavy Lanthanide Metallocenium Cations, *J. Am. Chem. Soc.*, 2017, **139**, 18714–18724.
- 82 D. K. Modder, M. S. Batov, T. Rajeshkumar, A. Sienkiewicz, I. Zivkovic, R. Scopelliti, L. Maron and M. Mazzanti, Assembling diuranium complexes in different states of charge with a bridging redox-active ligand, *Chem. Sci.*, 2022, **13**, 11294–11303.
- 83 W. R. Reed, M. A. Dunstan, R. W. Gable, W. Phonsri, K. S. Murray, R. A. Mole and C. Boskovic, Tetraoxolene-bridged rare-earth complexes: A radical-bridged dinuclear Dy single-molecule magnet, *Dalton Trans.*, 2019, **48**, 15635–15645.
- 84 K. Kotwica, I. Wielgus and A. Proń, Azaacenes based electroactive materials: preparation, structure, electrochemistry, spectroscopy and applications - a critical review, *Materials*, 2021, **14**, 5155.
- 85 K. Isoda, M. Nakamura, T. Tatenuma, H. Ogata, T. Sugaya and M. Tadokoro, Synthesis and characterization of electron-accepting nonsubstituted tetraazaacene derivatives, *Chem. Lett.*, 2012, **41**, 937–939.
- 86 J. U. Engelhart, B. D. Lindner, M. Schaffroth, D. Schrempp, O. Tverskoy and U. H. F. Bunz, Substituted tetraaza- and hexaazahexacenes and their N,N'-dihydro derivatives: Syntheses, properties, and structures, *Chem.-Eur. J.*, 2015, **21**, 8121–8129.
- 87 R. Orbach, Spin-lattice relaxation in rare-earth salts, *Proc. R. Soc. A*, 1961, **264**, 458–484.
- 88 R. Orbach, Spin-lattice relaxation in rare-earth salts: field dependence of the two-phonon process, *Proc. R. Soc. A*, 1961, **264**, 485–495.
- 89 N. Mavragani, A. A. Kitos, R. Gayfullina, A. Mansikkamäki, J. O. Moilanen and M. Murugesu, Exploring the substitution effect on the magnetic coupling of tetrazinyl-



- bridged Ln<sub>2</sub> single-molecule magnets, *Inorg. Chem. Front.*, 2025, **12**, 3403–3415.
- 90 S. Demir, M. I. Gonzalez, L. E. Darago, W. J. Evans and J. R. Long, Giant coercivity and high magnetic blocking temperatures for N<sub>2</sub><sup>3-</sup>-radical-bridged dilanthanide complexes upon ligand dissociation, *Nat. Commun.*, 2017, **8**, 2144.
- 91 C. A. Vasquez and S. Y. Fazzito, Simple hysteresis loop model for rock magnetic analysis, *Stud. Geophys. Geod.*, 2020, **64**, 114–129.
- 92 D. C. Jiles and D. L. Atherton, Theory of ferromagnetic hysteresis (invited), *J. Appl. Phys.*, 1984, **55**, 2115–2120.
- 93 T. Soda, Y. Kitagawa, T. Onishi, Y. Takano, Y. Shigeta, H. Nagao, Y. Yoshioka and K. Yamaguchi, *Ab initio* computations of effective exchange integrals for H-H, H-He-H and Mn<sub>2</sub>O<sub>2</sub> complex: Comparison of broken-symmetry approaches, *Chem. Phys. Lett.*, 2000, **319**, 223–230.
- 94 C. A. Gould, E. Mu, V. Vieru, L. E. Darago, K. Chakarawet, M. I. Gonzalez, S. Demir and J. R. Long, Substituent Effects on Exchange Coupling and Magnetic Relaxation in 2,2'-Bipyrimidine Radical-Bridged Dilanthanide Complexes, *J. Am. Chem. Soc.*, 2020, **142**, 21197–21209.
- 95 (a) F. Benner, S. Deshapriya and S. Demir, CCDC 2455536: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2nf5v4](https://doi.org/10.5517/ccdc.csd.cc2nf5v4); (b) F. Benner, S. Deshapriya and S. Demir, CCDC 2455829: Experimental Crystal Structure Determination, 2025, DOI: [10.5517/ccdc.csd.cc2nfh9x](https://doi.org/10.5517/ccdc.csd.cc2nfh9x).

