

Cite this: *Nanoscale Adv.*, 2022, 4, 5044

Pd/Ni-metal–organic framework-derived porous carbon nanosheets for efficient CO oxidation over a wide pH range†

Adewale K. Ipadeola,^a Kamel Eid,^b Aboubakr M. Abdullah,^c Rashid S. Al-Hajri^c and Kenneth I. Ozoemena^d

Metal nanocrystal ornamented metal–organic frameworks (MOFs) are of particular interest in multidisciplinary applications; however, their electrocatalytic CO oxidation performance over wide pH ranges is not yet reported. Herein, Ni-MOF-derived hierarchical porous carbon nanosheets (Ni-MOF/PC) with abundant Ni–N_x sites decorated with Pd nanocrystals (Pd/Ni-MOF/PC) were synthesized by microwave-irradiation (MW-I) followed by annealing at 900 °C and subsequent etching of Ni-MOF/C prior to Pd deposition. The fabrication mechanism comprises the generation of self-reduced reducing gases from triethylamine during the annealing and selective chemical etching of Ni, thereby facilitating the reduction of Ni-anchored MOF and Pd nanocrystal deposition with the aid of ethylene glycol and MW-I to yield Pd/Ni–N_x enriched MOF/PC. The synthetic strategies endear the Pd/Ni-MOF/PC with unique physicochemical merits: abundant defects, interconnected pores, high electrical conductivity, high surface area, Ni-deficient but more active sites for Pd/Ni–N_x in porous carbon nanosheets, and synergism. These merits endowed the CO oxidation activity and stability on Pd/Ni-MOF/PC substantially than those of Pd/Ni-MOF/C and Pd/C catalysts in wide pH conditions (*i.e.*, KOH, HClO₄, and NaHCO₃). The CO oxidation activity study reveals the utilization of MOF/PC with metal nanocrystals (Pd/Ni) in CO oxidation catalysis.

Received 15th July 2022
Accepted 4th September 2022

DOI: 10.1039/d2na00455k

rsc.li/nanoscale-advances

Introduction

Alcohol-based (ethanol,^{1,2} methanol,^{3,4} glucose⁵) fuel cells are green, sustainable, and effective energy sources; however, carbon monoxide (CO) poisoning^{6–8} is among the most crucial factors precluding the large-scale applications of such devices. CO oxidation is of great importance in multi-disciplinary industrial and environmental applications. There are various methods for CO oxidation, such as thermal,^{9–12} electrochemical,¹⁰ and photo-electrochemical,^{10,13} driven by various catalysts. Electrochemical CO oxidation is highly preferred environmentally owing to its lower energy demand and easy operation.¹⁴ Noble metals, particularly Pd-based catalysts, are the most impressive electrocatalysts for CO oxidation owing to

their outstanding ability to promote the adsorption/dissociation of reactants (*i.e.*, CO and O₂) alongside the oxidation of hydrogen under low applied potentials.^{14–21} However, the ceaseless price upsurge and earth scarcity, besides instability for the long-term, are the main stumbling blocks for large-scale applications. Various efforts were dedicated to solving these barriers in tailoring the size, shape, and lowering composition of Pd nanocrystals and their supports, thereby reducing the cost of the catalyst.^{14–23} Altering the d-band center of Pd by other metals allows the self-production of reactive oxygenated species (*i.e.*, ·OH radicals), which accelerate the CO oxidation kinetics and tolerate the adsorption of intermediates.^{14–21} For example, Pd nanodendrites enhanced the CO oxidation mass activity (58 mA mg_{Pd}^{−1}) by 1.9 fold than commercial Pd/C.²⁴ The CO oxidation activity and durability of Pd₄₀Ni₄₃P₁₇ outperformed the Pd/C catalyst, originating from the *in situ* formation of ·OH radicals on Ni active sites.²⁵ The CO oxidation mass activity of FePd nanocrystals (0.35 A mg_{Pd}^{−1}) was superior to that of Pd/C (0.18 A mg_{Pd}^{−1}) by 1.9 fold owing to tolerable CO_{ads} over FePd.²⁶ The CO oxidation activity and stability of Pd-based catalysts are augmented using supports, particularly carbon-based materials, due to their rich electron density, high electrical conductivity, and ability to stabilize Pd nanocrystals against aggregation. For example, Pd₄Au₁/C boosted the CO oxidation current density by 1.86 folds than Pt/C and 1.41 folds than Pd/C

^aCenter for Advanced Materials, Qatar University, Doha 2713, Qatar. E-mail: bakr@qu.edu.qa^bGas Processing Center (GPC), College of Engineering, Qatar University, Doha 2713, Qatar. E-mail: kamel.eid@qu.edu.qa^cPetroleum and Chemical Engineering Department, Sultan Qaboos University, Muscat, Oman. E-mail: rashidh@squ.edu.om^dMolecular Sciences Institute, School of Chemistry, University of the Witwatersrand, Private Bag 3, PO Wits, Johannesburg 2050, South Africa. E-mail: Kenneth.ozoemena@wits.ac.za† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2na00455k>

owing to Au effect.²⁷ Likewise, the CO oxidation activity of Pd₄₀Ru₅/graphene nanosheets (GNS) outperformed 40% Pd/GNs in KOH electrolyte.²⁸ The CO oxidation mass activity of Pd₁Sn_{0.40}/TiO₂-GO (~1500 mA mg_{Pd}⁻¹) was 6.07 folds greater than that of Pt₁Sn_{0.40}/TiO₂-GO and 8.82 folds than that of Pd₁Sn_{0.40}/C due to the presence of co-supports that enhance the CO_{ads}.²⁹

MOFs are new classes of materials and their carbonized derivatives have unique physiochemical properties of carbon and catalytic merits of metals (*i.e.*, high surface areas, multiple unsaturated coordination sites, well-crystalline structures, abundant active sites, and interior/exterior cavities), which can provide interconnected channels for reactants during CO oxidation.^{30–42} Moreover, MOFs with numerous unsaturated coordination sites and open inner/outer cavities can accommodate Pd nanocrystals, which results in higher stability aggregation and maximize Pd utilization during CO oxidation.^{38,43–47} There are a few reports on using MOFs and their derivatives as supports for Pd nanocrystals for thermal CO oxidation.^{38,43–48} However, the electrochemical CO oxidation performance of MOF-based catalysts with or without Pd nanocrystals is not yet reported to the best of our knowledge.^{38,43–47}

In pursuit of this aim, we rationally synthesized Pd/Ni-MOF/PC for electrocatalytic CO oxidation in different electrolytes. The synthesis approach is simple and green, comprising microwave irradiation, annealing, and etching of the sacrificial template (Ni-MOF/C) before Pd dispersion to form Pd/Ni-MOF/PC with porous carbon nanosheets and abundant Pd/Ni-N_x active sites. Unlike traditional preparation methods (*i.e.*, seed-mediated, solvothermal, and chemical reduction), microwave-irradiation is energy-efficient, environmentally benign, and provides a uniform heating mechanism utilizing dipolar polarization and ionic conduction, resulting in prompt nucleation and growth of small-sized Pd nanoparticles uniformly distributed over Ni-MOF/PC without the need for reducing agents or multiple reaction steps.^{49–53} The partially etched Ni-MOF/C resulted in more exposed Ni-N_x active sites and porous C in Pd/Ni-MOF/PC. The electrocatalytic CO oxidation performances of Pd/Ni-MOF/PC and without etching (Pd/Ni-MOF/C) are benchmarked with commercial Pd/C catalysts in KOH, HClO₄, and NaHCO₃.

Materials and methods

Materials

Nickel(II) nitrate hexahydrate (Ni(NO₃)₂·6H₂O, 94.5%), potassium palladium(II) chloride (K₂PdCl₄, 98%), trimesic acid (C₉H₆O₆, 95%), ethylene glycol ((EG), 99.8%), triethylamine (>99.5%), dimethylformamide (DMF, 99.8%), HClO₄, NaHCO₃ and KOH (>98%), commercial Pt/C (20 wt% Pt) and Pd/C catalyst (20 wt%) were purchased from Sigma-Aldrich Chemie GmbH (Munich, Germany).

Preparation of Ni-MOF-derived porous carbon (Ni-MOF/PC)

Ni-MOF/PC was synthesized by mixing Ni(NO₃)₂·6H₂O (0.44 g) and (0.36 g) of trimesic acid (0.36 g) in a mixture of

triethylamine (1.5 mL) and DMF (50 mL) under stirring at 25 °C. Then, the solution was poured into a Teflon container and subjected to microwave irradiation (at 600 W, 30 min). The precipitates obtained were washed and dried in a vacuum oven at 60 °C, followed by annealing at 900 °C for 4 h (5° min⁻¹ ramping rate) to yield Ni-MOF/C. The obtained powder was soaked in an aqueous solution of HCl (3 M) for 48 h to form Ni-deficient-MOF with enriched porous carbon nanosheets (Ni-MOF/PC).

Preparation of Pd/Ni-MOF/PC and Pd/Ni-MOF/C

Pd/Ni-MOF/PC and Pd/Ni-MOF/C were synthesized by mixing K₂PdCl₄ (61.35 mg) with EG (50 mL) under stirring at 25 °C for 30 min, and the pH was adjusted to 12 by KOH (1 M). Then, Ni-MOF/PC and Ni-MOF/C, respectively, were added. The solutions were placed in the microwave for irradiation at 600 W for 1 h. An aqueous solution of HCl (3 M) was used to lower the resulting solutions' pH (3), forming precipitates. The precipitates were washed with ethanol and H₂O and then dried at 80 °C for 24 h under a vacuum.

Materials characterization

The morphology and composition of the electrocatalysts were analyzed by a scanning electron microscope ((SEM), Hitachi S-4800, Hitachi, Tokyo, Japan) equipped with an energy dispersive X-ray analyzer (EDX) and a transmission electron microscope ((TEM), TecnaiG220, FEI, Hillsboro, OR, USA). Their electronic structures and surface compositions were analyzed using X-ray photoelectron spectroscopy (XPS), Ultra DLD XPS Kratos, Manchester, UK). The crystallinity was investigated by X-ray diffraction (XRD, X'Pert-Pro MPD, PANalytical Co., Almelo, Netherlands). Raman spectra were recorded on a Raman instrument (Thermo Scientific) under 532 nm laser excitation. Inductively coupled plasma optical emission spectrometry (ICP-OES, Agilent 5800 DV) was used to estimate the catalyst loading on working electrodes. Brunauer–Emmett–Teller (BET) surface area analysis (Horiba SA-9600) was performed to determine the specific surface area, pore volume, and pore sizes.

CO oxidation reaction

The electrochemical CO oxidation was carried out on a Gamry potentiostat (Reference 3000, Gamry Co., Warminster, PA, USA) using the three-electrode cell involving Pt wire, Ag/AgCl, and glassy carbon (GC), as counter, reference, and the working electrodes, respectively. 2 mg of each catalyst was dispersed in an aqueous solution of isopropanol/H₂O (3/1 v/v ratio) and drop-casted onto the GC electrodes, 3 μL of Nafion solution (0.05 wt%) was added, and electrodes were left to dry in an oven under vacuum at 80 °C for 1 h. The loading of Pd in the electrocatalysts on the GCE was approximately 0.020 ± 0.002 mg_{Pd} cm⁻², as determined by ICP-OES. The electrochemical active surface area (ECSA) was calculated by the integration of hydrogen under-potential adsorption/desorption (HUPD) from CV curves. All the potentials were calibrated to a reversible hydrogen electrode (RHE), according to the equation: $E(\text{RHE}) = E(\text{Ag}/\text{AgCl}) + 0.197V + 0.059 \times \text{pH}$.



Results and discussion

Fig. 1a shows the synthesis process of Pd/Ni-MOF/PC as outlined: the Ni-MOF template prepared by microwave irradiation was subsequently annealed under N_2 to afford abundant Ni nanocrystals anchored on the N_x -sites of MOF/C with the assistance of the self-reduced gases (*i.e.*, NH_3 , C_xH_y , and H_2) emitted from triethylamine at a high carbonization temperature. Then, the selective chemical etching of Ni-MOF/C in HCl allows the partial removal of Ni nanocrystals to produce porous carbon nanosheets with abundant defects and cavities (*i.e.*, Ni-MOF/PC) due to the instability of Ni in acidic solutions. The microwave-illumination of Ni-MOF/PC and Ni-MOF/C in an

ethylene glycol solution containing Pd produced Pd nanocrystal-ornamented Ni-MOF/PC (Pd/Ni-MOF/PC) and Pd/Ni-MOF/C, respectively, owing to the reduction and microwave absorption power of ethylene glycol.^{22,54} Fig. 1b shows the SEM image of Pd/Ni-MOF/C with a stacked sheet-like morphology without any obvious porosity, and the TEM image reveals the good distribution of Pd/Ni nanocrystals in a spherical-like shape over carbon nanosheets (Fig. S1a†).

The average diameter of Pd nanocrystals is about 10.8 nm (Fig. S1b†). The TEM image of Pd/Ni-MOF/C displays the lattice fringes of Pd nanocrystals without any crystalline defects with an interlayer spacing of 0.22 nm assigned to the {111} facet of face-centered cubic (fcc) Pd in addition to the amorphous-



Fig. 1 (a) The preparation process of Pd/Ni-MOF/PC. (b) SEM image of Pd/Ni-MOF/PC and its (c) SEM image, (d) TEM image, (e) HRTEM image, (f–i) Fourier filtered HRTEM images of the numbered areas (1–4) in (e), respectively, (j) SAED, (k), HADDF-STEM image of Pd/Ni-MOF/PC and its (l–o) elemental mapping analysis of the marked area in (k). (p) EDX analysis of Pd/Ni-MOF/PC and Pd/Ni-MOF/C.



crystalline structure of carbon as indicated by the arrows in Fig. S1c.† The selected area electron diffraction (SAED) patterns imply the typical diffraction rings ascribed to the {111}, {200}, {220}, {311}, and {222} crystal planes of fcc Pd (Fig. S1d†), as usually observed for Pd nanocrystals. The etching of Ni-MOF/C by HCl in Pd/Ni-MOF/PC yields well-defined hierarchical porous nanosheets with interconnected pores and diameters ranging from 5 to 50 nm due to the partial etching of Ni nanocrystals (Fig. 1c). The interconnected pores are important for facilitating CO absorption and migration along with maximizing the utilization of buried Pd and Ni during CO oxidation. The TEM image of Pd/Ni-MOF/PC displays the uniform distribution of Pd nanocrystals over porous carbon nanosheets (Fig. 1d). The average size of thus formed Pd nanocrystals in Pd/Ni-MOF/PC is 7.5 nm, which decreased significantly relative to Pd/Ni-MOF/C, owing to the etching effect and instability of Ni nanocrystals in acidic solutions (Fig. S2†).^{55,56} The HRTEM image of Pd/Ni-MOF/PC reveals the lattice fringes of Pd nanocrystals and amorphous-crystalline structure of carbon, as indicated by the arrows (Fig. 1e). The Fourier-filtered HRTEM images of Pd nanocrystals demonstrate the lattice fringes with multiple crystalline defects, such as interfacial dislocation, intragranular dislocation, and stacking fault, as indicated by the arrows (Fig. 1f–i). The estimated interplanar spacings 2.236, 1.936, 1.369, 1.170, and 1.116 Å are assigned to the {111}, {200}, {220}, {311}, and {222} facets of face-centered-cubic (fcc) of Pd, respectively, as usually observed in Pd-based catalysts.⁵⁷ This is in line with the SAED patterns, which reveal the diffraction rings ascribed to fcc Pd (Fig. 1j). The HAADF-STEM of Pd/Ni-MOF/PC discloses the formation of hierarchical porous nanosheets (Fig. 1k). The element mapping analysis validates the presence of C, N, Ni, and Pd in Pd/Ni-MOF/PC with atomic contents of 54.12, 8.02, 15.08, and 22.15%, respectively (Fig. 1l–o), as further proved by the EDX analysis (Fig. 1p). The EDX analysis of Pd/Ni-MOF/C depicts the co-existence of Pd, Ni, C, O, and N with the atomic contents of 10.29, 20.80, 47.86, 10.79, and 10.44% in Pd/Ni-MOF/C, respectively (Fig. 1p). The presence of O in Pd/Ni-MOF/C is plausibly due to the instability of Ni in air resulting in the formation of passivating oxide layers over Ni, which disappear after etching and possibly allow Pd–Ni_x coordination in Pd/Ni-MOF/PC.

Notably, in the absence of microwave irradiation, we could not obtain Pd nanoparticles, implying the significant effect of microwave irradiation to allow the reduction of the Pd precursor and form Pd nanoparticles without the use of a reducing agent. This is plausibly due to the uniform heating mechanism, dipolar polarization, and ionic conduction effect of microwave irradiation. The XRD of Pd/Ni-MOF/PC and Pd/Ni-MOF/C shows the diffraction patterns assigned to the (111), (200), (220), (311), and (222) facets of fcc Pd besides (111), (200) and (220) of fcc Ni, and (002) facet of graphitic C (Fig. 2a). The Pd(111) and Ni(111) facets dominate in both Pd/Ni-MOF/PC and Pd/Ni-MOF/C. The presence of the XRD diffraction patterns of Ni plausibly indicates the formation of Ni nanocrystals due to the *in situ* reducing gases generated from triethylamine during microwave irradiation and annealing.⁴⁸ The diffraction patterns of Pd/Ni-MOF/PC are broadened with lower intensity relative to

Pd/Ni-MOF/C due to crystals defects and the Pd/Ni–N_x–C ligand effect. That is also evidenced in the slight positive shift in the 2θ angle value of Pd/Ni-MOF/PC compared to Pd/Ni-MOF/C and commercial Pd/C. The Pd/Ni–N_x–C ligand effect in Pd/Ni-MOF/PC leads to a decrease in the Pd–Pd interatomic distance, as seen in the lower lattice parameter value (*a*) of Pd/Ni-MOF/PC (0.27 nm) than Pd/Ni-MOF/C (0.29 nm) and Pd/C (0.31 nm), serving as an evidence of higher defects in Pd/Ni-MOF/PC. The average crystallite size of Pd/Ni-MOF/PC (4.0 nm) is lower than that of Pd/Ni-MOF/C (7 nm) and Pd/C (8 nm) as obtained from the (111) peak using Scherrer's equation.

The XPS full-scan of Pd/Ni-MOF/PC and Pd/Ni-MOF/C implies the presence of Pd 3d, Ni 2p, C 1s, N 1s and O 1s (Fig. 2b). The deconvolution of Pd 3d spectra in both Pd/Ni-MOF/PC and Pd/Ni-MOF/C shows Pd⁰ 3d_{5/2} and Pd⁰ 3d_{3/2} as the main metallic phase in addition to the small peaks of PdO (Pd²⁺ 3d_{5/2} and Pd²⁺ 3d_{3/2}), owing to the high reduction feature of ethylene glycol under microwave illumination (Fig. 2c and d). The fitting of Ni 2p spectra (Fig. 2e and f) reveals intense peaks for Ni⁰ 2p_{3/2} and Ni⁰ 2p_{1/2} as the main phase and NiO peak as a minor phase, but the ratio of the Ni metallic phase to the NiO phase in Pd/Ni-MOF/PC is higher than in Pd/Ni-MOF/C due to the etching effect. The presence of Ni in the metallic phase is in line with the XRD results that further infer the formation of Ni nanocrystals in Pd/Ni-MOF/PC but Ni and NiO nanocrystals in Pd/Ni-MOF/C. The C 1s spectra comprise two intensive peaks for C-bonded to metal (M–C), sp²/sp³ of C–C, and a small shoulder for N–C=O in Pd/Ni-MOF/C (Fig. 2g), but a strong peak for C–C, low M–C and N–C=O were present in Pd/Ni-MOF/PC (Fig. 2h). The O 1s spectra show lattice O (O_L) and surface O (O_S) in Pd/Ni-MOF/C (Fig. 2i), but O_L and O vacancy (O_V) in Pd/Ni-MOF/PC (Fig. 2j). The O_V in Pd/Ni-MOF/PC implies the removal of a passivating oxide layer and generation of defects by HCl etchant. The N 1s spectra display pyridinic N (398.1 eV), metal–N species (399.2 eV), pyrrolic N (401.2 eV), and graphitic N (402.2 eV) in both Pd/Ni-MOF/C (Fig. 2k) and Pd/Ni-MOF/PC (Fig. 2l). The presence of metal–N species in both Pd/Ni-MOF/C and Pd/Ni-MOF/PC supports the atomic dispersion of Ni–N_x and its coordination with Pd.

The Raman spectra of Pd/Ni-MOF/PC and Pd/Ni-MOF/C show a graphitic (G) band at ~1591 cm⁻¹ assigned to the crystalline graphite sp² carbon basal plane and a defective (D) band of sp³ carbon at ~1333 cm⁻¹ (Fig. S3a†). The broadened and decreased intensity of D and G peaks of Pd/Ni-MOF/PC relative to Pd/Ni-MOF/C are due to the etching effect, which generates various structural defects. That is additionally seen in the higher ratio of (I_D/I_G) of Pd/Ni-MOF/PC (0.98) than Pd/Ni-MOF/C (0.86). The structural defects of Pd/Ni-MOF/PC could act as active sites for boosting the adsorption of reactant molecules during CO oxidation.

The FTIR analysis is accrued to get more insights into the chemical nature of Pd/Ni-MOF/PC and Pd/Ni-MOF/C, which both show strong absorption peaks of the stretching mode of C=C, C–N heterocycles, and N–H (Fig. S3b†). The broadening of the N–H peak could serve as an indication for Ni–N_x coordination in both Pd/Ni-MOF/PC and Pd/Ni-MOF/C. Noticeably, broader Pd/Ni-MOF/PC peaks with less intensity compared to its



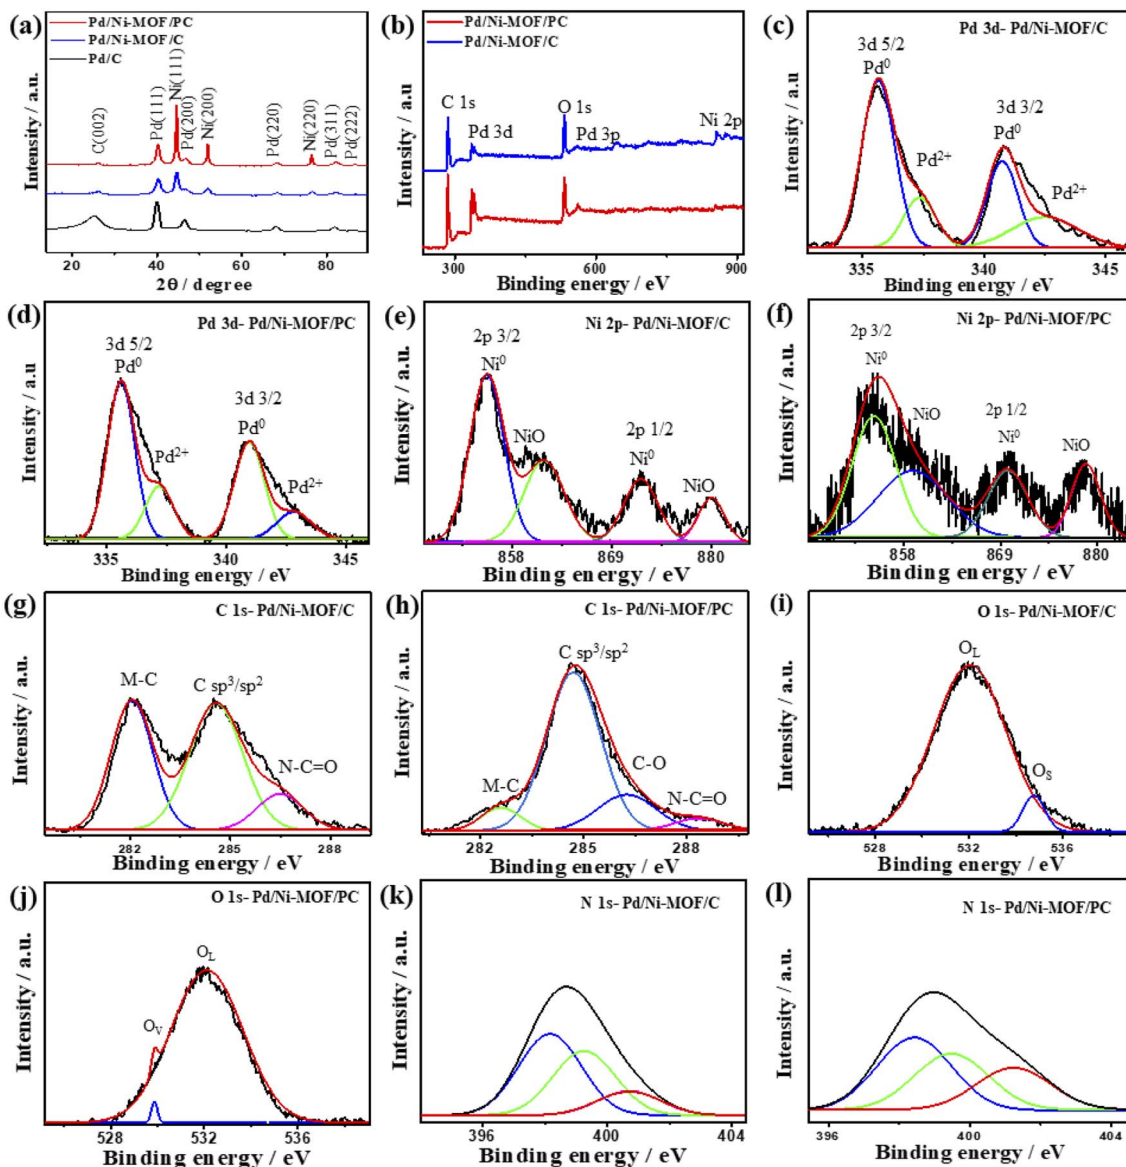


Fig. 2 (a) XRD, (b) XPS survey, high-resolution XPS spectra of (c and d) Pd 3d, (e and f) Ni 2p, (g and h) C 1s, (i and j) O 1s and (k and l) N 1s of Pd/Ni-MOF/C and Pd/Ni-MOF/PC, respectively.

counterpart (Pd/Ni-MOF/C) are ascribable to the etching effect.²²

The pore size, pore volume, and surface area of electrocatalysts are investigated with BET analysis, where Pd/Ni-MOF/PC has a high pore size (7.60 nm), pore volume ($0.1240 \text{ cm}^3 \text{ g}^{-1}$), and surface area ($153.0463 \text{ m}^2 \text{ g}^{-1}$) than Pd/Ni-MOF/C (6.15 nm, $0.1049 \text{ cm}^3 \text{ g}^{-1}$, and $142.2231 \text{ m}^2 \text{ g}^{-1}$) (Table S1†). Also, well-distributed pore size and pore volume for the adsorption of gas is evidenced by the hierarchical pores of Pd/Ni-MOF/PC (Fig. S3c and d†). These results corroborate more interconnected pores and surface area of Pd/Ni-MOF/PC for the easy diffusion of intermediates or gases during CO oxidation electrocatalysis. ICP-OES was utilized to determine the metal contents in the electrocatalysts. Pd/Ni-MOF/PC has Pd ($14.26 \pm 0.25 \text{ wt}\%$) and Ni ($14.40 \pm 0.69 \text{ wt}\%$), while Pd/Ni-MOF/C has Pd

($21.40 \pm 1.05 \text{ wt}\%$) and Ni ($43.12 \pm 0.91 \text{ wt}\%$). The results show that although Pd/Ni-MOF/PC has lower metal contents than Pd/Ni-MOF/C, the etching tuned its physicochemical properties for boosted CO oxidation.

The electrochemical CO oxidation activity of Pd/Ni-MOF/PC and Pd/Ni-MOF/C is benchmarked to commercial Pd/C catalysts in different electrolytes. Fig. 3a shows the cyclic voltammograms (CV) of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C, measured in the N_2 -saturated HClO_4 electrolyte, which showed the voltammogram features of Pd electrocatalysts. This includes the double-layered hydrogen-adsorption/desorption (HUPD) between 0.36 V and 0.50 V and Pd-H between 0.09 V and 0.33 V, and Pd-O reduction between 0.53 V and 0.91 V without any significant peaks for Pd-O or Ni-O, which imply their stability against oxidation. Notably, the HUPD of Pd/Ni-MOF/PC is



significantly higher than that of Pd/Ni-MOF/C, indicating its higher active sites and ECSA. Thereby, the ECSA of Pd/Ni-MOF/PC showed higher ECSA ($69 \text{ m}^2 \text{ g}^{-1}$), which is 2.3 times of Pd/Ni-MOF/C ($30 \text{ m}^2 \text{ g}^{-1}$) and 30 times of Pd/C ($2 \text{ m}^2 \text{ g}^{-1}$), due to the porosity, structural defects, and enhanced active sites of Pd/Ni-MOF/PC. The CV curves measured in the CO-purged HClO_4 electrolyte of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C show the CO-oxidation voltammogram features, including a sharp anodic oxidation current (I_{anode}) in the positive potential region (*i.e.*, 0.81 to 1.21 V vs. RHE), and reduction current ($I_{\text{reduc.}}$) in the negative potential region along with HUPD. Both Pd/Ni-MOF/PC and Pd/Ni-MOF/C infer two noticeable I_{anode} peaks, plausibly owing to the Pd-Ni-N_x ligand effect. The CO oxidation activity of Pd/Ni-MOF/PC is superior to that of Pd/Ni-MOF/C and Pd/C (Fig. 3b). The I_{anode} of Pd/Ni-MOF/PC (4.71 mA cm^{-2}) is 3.4 folds higher than that of Pd/Ni-MOF/C (1.38 mA cm^{-2}) and 5.0 folds that of Pd/C (0.95 mA cm^{-2}). This is due to the porous morphology, which maximizes the utilization of Pd-Ni-N_x in Pd/Ni-MOF/PC during the CO oxidation reaction. Intriguingly, the I_{anode} of Pd/Ni-MOF/PC (4.71 mA cm^{-2}) is superior to that of previously reported PtRu, Pt/SnO_x, Pd/Ti₃C₂T_x, and PtBi nano-sponge measured under similar conditions (Table S2†).^{5,58–60} The CO oxidation potential (E_{oxi}) of Pd/Ni-MOF/PC (1.05 V) is lower than that of Pd/Ni-MOF/C (1.06 V) by 0.01 V and Pd/C

(1.17 V) by 0.012 V, implying fast CO oxidation kinetics on Pd/Ni-MOF/PC (Fig. S4a†). That is further seen in the lower onset potential (E_{onset}) of Pd/Ni-MOF/PC (0.84 V) than those of Pd/Ni-MOF/C (0.88 V) and Pd/C (1.10 V). The linear sweep voltammogram (LSV) also shows better CO oxidation kinetics on Pd/Ni-MOF/PC, as evidenced in its ability to deliver a higher I_{anode} than Pd/Ni-MOF/C and Pd/C under an applied potential (Fig. 3c), owing to the greater defects, higher electrical conductivity, and synergism of Pd-Ni-N_x in Pd/Ni-MOF/PC. The CVs measured at various sweeping rates from 25 to 300 mV s^{-1} reveal the progressive rise of the I_{anode} with increasing scan rates (ν) on all measured catalysts (Fig. 3d–f).

Plotting I_{anode} vs. $\nu^{1/2}$ shows a linear relationship that infers a diffusion-controlled process of CO oxidation on all catalysts, but Pd/Ni-MOF/PC displays a greater magnitude of slope (*i.e.*, 1.03) than Pd/Ni-MOF/C (0.77) and Pd/C (0.20) (Fig. 3g), serving as evidence for quicker ionic diffusion on Pd/Ni-MOF/PC. The chronoamperometry (CA) tests measured for 1200 s show the greater stability of Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C catalysts, as designated by its higher current retention (Fig. S4b†). This is also shown in the CVs measured after CA tests, which unveil the same CO oxidation voltammogram features on all catalysts but with superior activity and durability on Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C (Fig. 4a–c). The

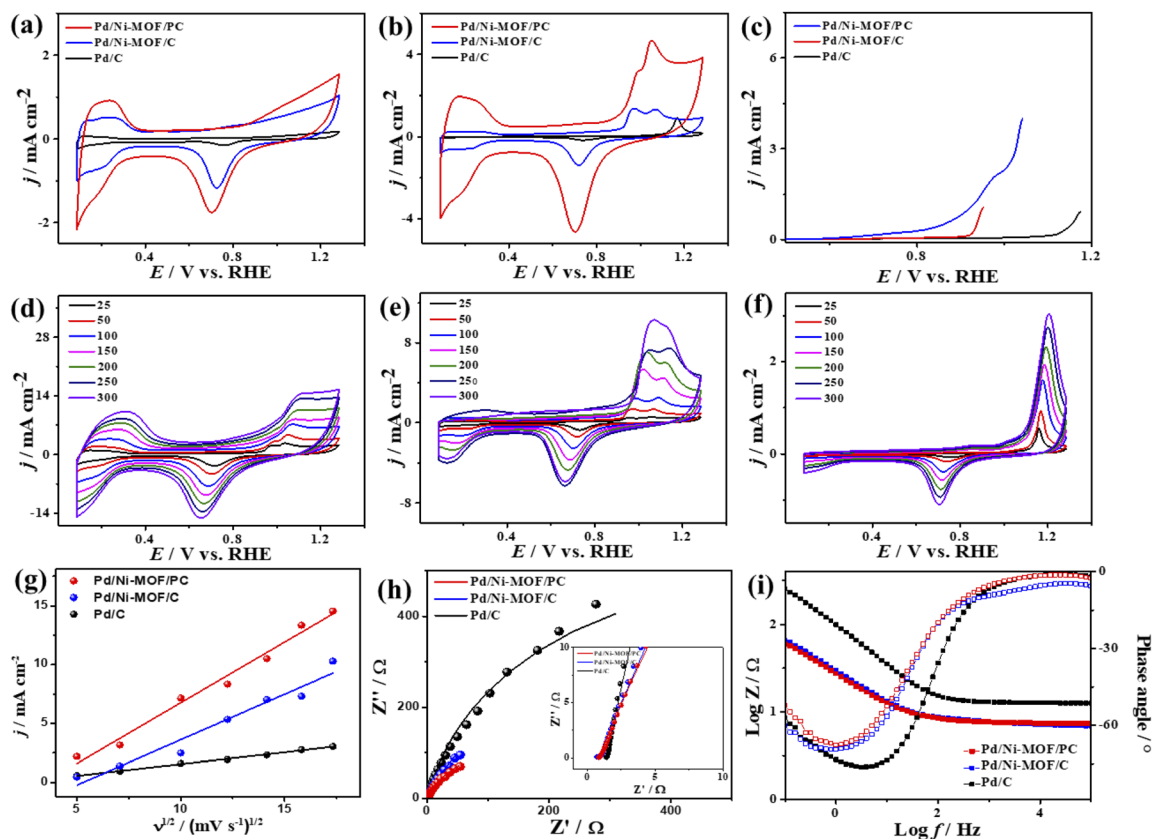


Fig. 3 (a) CV in 0.1 M HClO_4 , (b) CV in CO-purged 0.1 M HClO_4 , (c) LSV in CO-saturated 0.1 M HClO_4 of Pd/Ni-MOF-PC, Pd/Ni-MOF-C, and commercial Pd/C. CV measured in CO-saturated 0.1 M HClO_4 at different scan rates of (d) Pd/Ni-MOF/C, (e) Pd/Ni-MOF/PC, (f) Pd/C, and (g) their related plots of current density vs. square root of scan rates. (h) Nyquist plots and (i) Bode plots measured in CO-saturated 0.1 M HClO_4 electrolyte of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C.



Pd/Ni-MOF/PC maintained 19.4% of its I_{anode} relative to Pd/Ni-MOF/C (72.7%) and Pd/C (63.8%) (Fig. 4d), demonstrating the significant CO oxidation stability of Pd/Ni-MOF/PC. The TEM image measured after stability tests infers the porous 2D nanosheets ornamented with Pd nanocrystals without apparent aggregation or leaching, implying structural durability (Fig. S5†).




The interfacial interaction of the electrocatalysts with CO-saturated HClO_4 electrolytes was probed using electrochemical impedance spectroscopy (EIS), which shows a semi-circle shape but with a lower diameter on Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C, implying a better charge transfer across the electrolyte-electrode interface on Pd/Ni-MOF/PC (Fig. 3h).¹⁰ That is evidenced in fitting the Nyquist plots using the Voigt electrical equivalent circuit (Fig. S4c†) to estimate the electrolyte resistance (R_s), charge transfer resistance (R_{ct}), and constant phase element (CPE) (Table 1). Pd/Ni-MOF/PC has the lowest R_s and R_{ct} than Pd/Ni-MOF/C and Pd/C, indicating the quickest charge transfer across the electrolyte/electrode and lower charge mobility resistance on Pd/Ni-MOF/PC, which enhanced the CO oxidation. To get more insights into the CO oxidation process, we use the CPE with deviation (a) from an ideal double-layer capacitor (C_{dl}) and Bode plots (Fig. 3i),⁶¹ which reveals an ideality factor of ($0.5 < a < 1$), and a lower charge mobility resistance on Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C. This indicates that CO oxidation is a diffusion-controlled process coupled with the adsorption process on Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C. The phase angle in the range of $67\text{--}80^\circ$ for all the catalysts further verifies that CO oxidation occurs *via* CO adsorption and diffusion-controlled processes.⁶²

Thus, the CO oxidation mechanism on Pd/Ni-MOF/PC probably follows a Langmuir-Hinshelwood type reaction (eqn (i)–(iii)). This process includes the initial adsorption of CO (CO_{ads}) on Pd/Ni-MOF/PC to form ($\text{CO}_{\text{ads}}/\text{Pd/Ni-MOF/PC}$), and simultaneously, CO_{ads} -free Pd nanocrystals promote H_2 oxidation to produce OH adsorbed on Pd/Ni-MOF/PC ($\text{OH}_{\text{ads}}/\text{Pd/Ni-MOF/PC}$).⁶³ Consequently, CO_2 is formed by the oxidation of

Table 1 EIS data for catalysts in CO-purged 0.1 M HClO_4 electrolyte

| | R_s/Ω | R_{ct}/Ω | CPE/ $\mu\text{S s}^a$ | a |
|--------------|-----------------|-------------------|------------------------|------|
| Pd/C | 1.42 ± 0.22 | 272.70 ± 5.43 | 96.99 ± 1.04 | 0.79 |
| Pd/Ni-MOF/C | 0.89 ± 0.17 | 61.27 ± 1.13 | 359.20 ± 3.45 | 0.87 |
| Pd/Ni-MOF/PC | 0.83 ± 0.20 | 58.25 ± 0.51 | 228.20 ± 2.50 | 0.85 |

CO_{ads} by OH_{ads} with the assistance of the oxophilic effect of Ni- N_x and then desorbed from the surface of Pd/Ni-MOF/PC. Owing to the porosity of Pd/Ni-MOF/PC, its active sites are more accessible for the reactants, and induced quick generation of OH species with the assistance of Ni- N_x promotes the CO oxidation activity.⁶³



M^* is the active site “Pd-Ni- N_x ” of the catalyst, and ads is the adsorbed species.

The CV curves of the catalysts measured in KOH electrolyte only show the ideal voltammogram features of Pd-based catalysts but with a greater HUPD of Pd/Ni-MOF/PC and Pd/Ni-MOF/C than that of Pd/C, originating from their higher ECSA (Fig. 5a). The ECSA of Pd/Ni-MOF/PC ($87.0 \text{ m}^2 \text{ g}^{-1}$) was 1.56 and 6.59 times higher than that of Pd/Ni-MOF/C ($55.7 \text{ m}^2 \text{ g}^{-1}$) and Pd/C ($13.2 \text{ m}^2 \text{ g}^{-1}$). The CVs measured in CO-saturated KOH reveal the CO oxidation voltammogram with an apparent I_{anode} and I_{cathode} but with a grander activity of Pd/Ni-MOF/PC. The I_{anode} of Pd/Ni-MOF/PC (3.94 mA cm^{-2}) is greater than that of Pd/Ni-MOF/C (2.65 mA cm^{-2}) and Pd/C (1.37 mA cm^{-2}) by 1.48 and 2.87 times, respectively. This implies the maximized utilization of Pd-Ni- N_x during CO oxidation on Pd/Ni-MOF/PC due to the nanosheet morphology with interconnected pores. That is seen in the higher I_{anode} of Pd/Ni-MOF/PC than that of Pd/Ni-MOF/C and Pd/C under any applied potential, implying the enhanced CO oxidation kinetics on Pd/Ni-MOF/PC (Fig. 5b and c). That is additionally seen in the earlier $E_{\text{onset}}/E_{\text{oxi}}$ of Pd/Ni-MOF/PC (0.65 V/0.74 V) relative to Pd/Ni-MOF/C (0.53 V/0.73 V) and Pd/C (0.70 V/0.75 V) (Fig. S6a†). The I_{anode} increased steadily with increasing ν from 25 to 300 mV s^{-1} on the as-synthesized catalysts but with higher I_{anode} values on Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C (Fig. 5d–f). The linear relationship between I_{anodic} and $\nu^{1/2}$ suggests the diffusion-controlled process of CO oxidation. However, Pd/Ni-MOF/PC reveals a larger line slope of (0.71) than Pd/Ni-MOF/C (0.70) and Pd/C (0.35) (Fig. 5g). That serves as a proof of the better charge mobility kinetics on Pd/Ni-MOF/PC, as proved by the EIS.¹⁰ The Nyquist plots of EIS display semicircle curves but Pd/Ni-MOF/PC shows a significantly lower semicircle diameter than Pd/Ni-MOF/C and Pd/C (Fig. 5h), implying a better electrolyte-electrode interaction and quicker charge mobility on Pd/Ni-MOF/PC. That is seen in the lower R_s and R_{ct} besides a greater

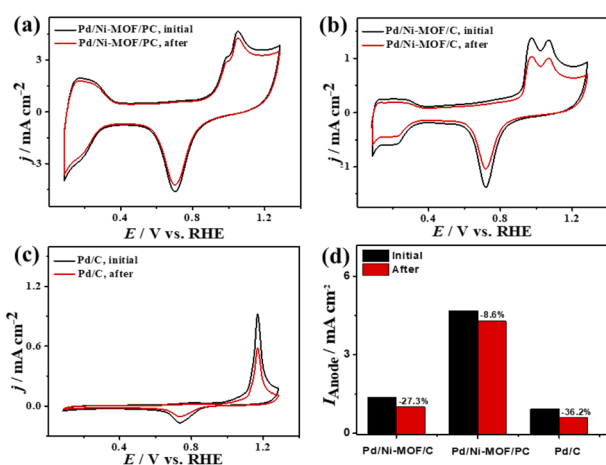


Fig. 4 (a–c) CV stability of CO oxidation and (d) I_{anode} stability of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C in CO-saturated 0.1 M HClO_4 electrolyte.



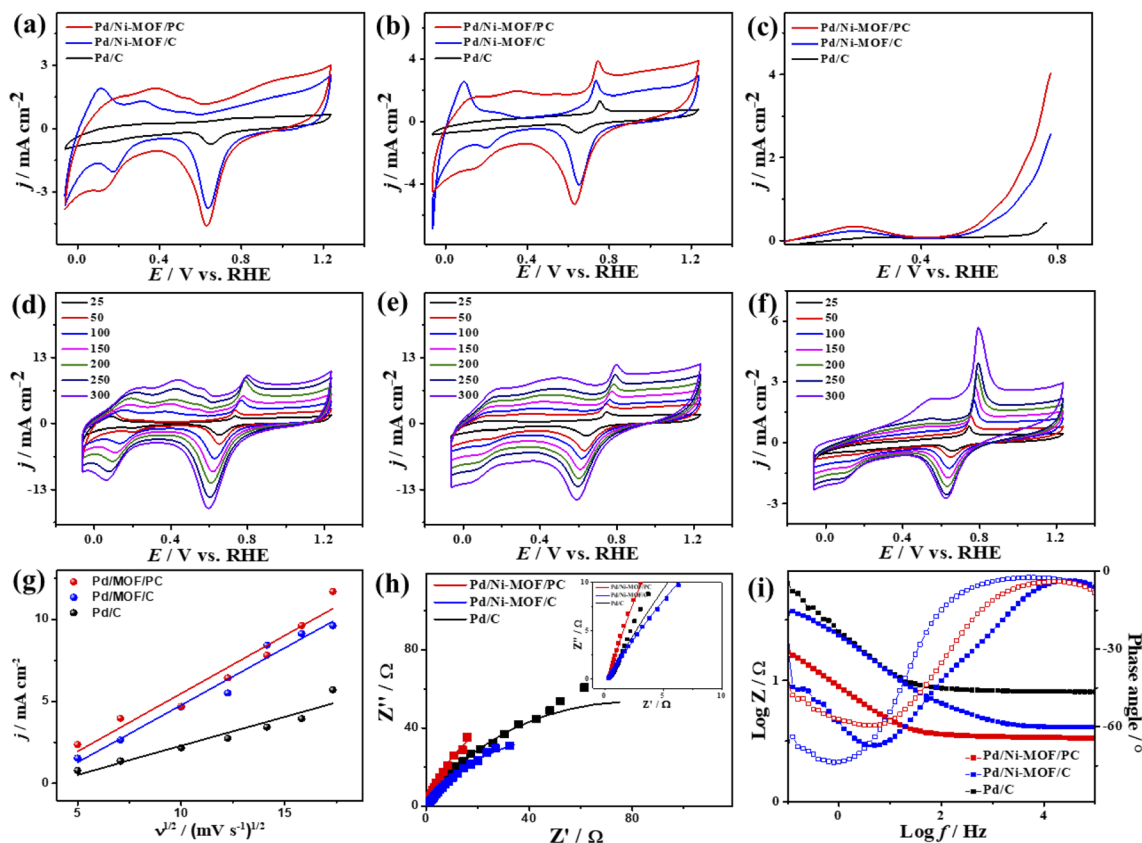


Fig. 5 (a) CV in 0.1 M KOH, (b) CV in CO-saturated 0.1 M KOH, and (c) LSV in CO-saturated 0.1 M KOH of Pd/Ni-MOF-PC, Pd/Ni-MOF-C, and commercial Pd/C. CV measured in CO-saturated 0.1 M KOH at different scan rates of (d) Pd/Ni-MOF/PC, (e) Pd/Ni-MOF/C, and (f) Pd/C and their (g) related plots of current density vs. square root of scan rates, (h) Nyquist plots and (i) Bode plots measured in CO-saturated 0.1 M KOH electrolyte of Pd/Ni-MOF/PC, Pd/Ni-MOF/C and Pd/C.

CPE on Pd/Ni-MOF/PC relative to Pd/Ni-MOF/C and Pd/C (Table 2).

The ideality factor ($0.5 < a < 1$) of the catalysts for modeling with CPE rather than C_{dl} confirms the porous and heterogenous nature of the electrode surface rather than an ideal smooth surface. The phase angle in the range of $60\text{--}80^\circ$ for all the catalysts further corroborates that the CO oxidation in the KOH electrolyte occurs on a heterogenous porous surface of pseudocapacitive property rather than an ideal double layer. Intriguingly, the I_{anode} of Pd/Ni-MOF/PC (3.94 mA cm^{-2}) is superior to that of previously reported PdAg/C⁶⁴ and PtNi multicubes⁶⁵ and other catalysts measured under similar conditions (Table S2†). The CA (Fig. S6b†) measured for 2000 s in CO-saturated 0.1 M KOH electrolyte designates the higher CO oxidation durability of Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C, as shown in the inferior current degradation. Meanwhile,

the CV tests measured after CA on all catalysts sustained the initial CO oxidation voltammogram features but with superior stability of Pd/Ni-MOF/PC. To this end, the I_{anode} of Pd/Ni-MOF/PC diminished only by 6.0% compared with Pd/Ni-MOF/C (21.3%) and Pd/C (27.2%) (Fig. 6a–d). The CVs measured in 0.1 M NaHCO₃ demonstrate the voltammogram merits of Pd-based catalysts but with a higher HUPD of Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C, inferring its higher ECSA (Fig. 7a). The ECSA of Pd/Ni-MOF/PC ($14.75 \text{ m}^2 \text{ g}^{-1}$) is 3.2 times that of Pd/Ni-MOF/C ($4.55 \text{ m}^2 \text{ g}^{-1}$) and 4.03 times that of Pd/C ($3.66 \text{ m}^2 \text{ g}^{-1}$), inferring the greater active sites of Pd/Ni-MOF/PC. The CV curves measured in CO-saturated NaHCO₃ reveal the CO oxidation voltammogram with apparent I_{anode} and I_{cathode} in the potential, but with a significantly higher activity of Pd/Ni-MOF/PC (Fig. 7b). The I_{anode} of Pd/Ni-MOF/PC (1.26 mA cm^{-2}) is greater than that of Pd/Ni-MOF/C (0.55 mA cm^{-2}) by 2.29 times and Pd/C (0.53 mA cm^{-2}) by 2.3 times, implying the maximized atomic utilization of Pd–Ni–N_x in Pd/Ni-MOF/PC, owing to its hierarchal porous structure. The LSV reveals the ability of Pd/Ni-MOF/PC to deliver higher I_{anode} under any applied potential than Pd/Ni-MOF/C and Pd/C, implying the quick CO oxidation kinetics on Pd/Ni-MOF/PC (Fig. 7c).

That is additionally seen in the substantially lower $E_{\text{onset}}/E_{\text{oxi}}$ (Fig. S7a†) of Pd/Ni-MOF/PC ($0.73 \text{ V}/0.83 \text{ V}$) relative to Pd/Ni-

Table 2 EIS data for catalysts in CO-purged 0.1 M KOH electrolyte

| | R_s/Ω | R_{ct}/Ω | CPE/ $\mu\text{S s}^a$ | a |
|--------------|-----------------|------------------|------------------------|------|
| Pd/C | 0.35 ± 0.02 | 62.32 ± 0.43 | 133.53 ± 3.72 | 0.79 |
| Pd/Ni-MOF/C | 0.34 ± 0.07 | 34.65 ± 0.31 | 409.09 ± 5.14 | 0.91 |
| Pd/Ni-MOF/PC | 0.33 ± 0.02 | 16.99 ± 0.48 | 513.04 ± 5.31 | 0.89 |





Fig. 6 (a–c) CV of CO oxidation durability and (d) I_{anode} stability of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C in CO-saturated 0.1 M KOH electrolyte.

MOF/C (0.75 V/0.85 V) and Pd/C (0.97 V/1.05 V). A similar CO oxidation activity trend was observed with LSV. The I_{anode} increased steadily with increasing ν from 25 to 300 mV s^{-1} on the as-synthesized catalysts but with a higher I_{anode} value on Pd/

Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C (Fig. 7d–f). The linear relationship among I_{anode} vs. $\nu^{1/2}$ (Fig. 7g) suggests the diffusion-controlled process of CO oxidation. However, Pd/Ni-MOF/PC exposes a larger slope of (0.39) than Pd/Ni-MOF/C (0.15) and Pd/C (0.13), suggesting fast CO diffusion on the Pd/Ni-MOF/PC. The Nyquist plots of EIS measured on all electrocatalysts reveal a semicircle line but with a smaller diameter of Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C (Fig. 7h), implying the better electrolyte–electrode interaction and quicker charge mobility on Pd/Ni-MOF/PC. That is seen in the lower R_s and R_{ct} besides a greater CPE on Pd/Ni-MOF/PC relative to Pd/Ni-MOF/C and Pd/C (Table 3). The ideality factor ($0.5 < a < 1$) of the catalysts for modeling with CPE rather than C_{dl} reveals that their CO oxidation is a diffusion-controlled process coupled to the adsorption process. The CAS (Fig. S7b†) measured for 1200 s

Table 3 EIS data for catalysts in CO-purged 0.1 M NaHCO_3 electrolyte

| | R_s/Ω | R_{ct}/Ω | $\text{CPE}/\mu\text{s s}^{-a}$ | a |
|--------------|-----------------|------------------------|---------------------------------|------|
| Pd/C | 1.15 ± 0.09 | 234.69 ± 3.37 | 25.74 ± 0.26 | 0.88 |
| Pd/Ni-MOF/C | 0.98 ± 0.04 | 102.89 ± 2.19 | 66.85 ± 0.68 | 0.77 |
| Pd/Ni-MOF/PC | 0.68 ± 0.03 | 26.42 ± 1.53 | 217.10 ± 2.15 | 0.82 |

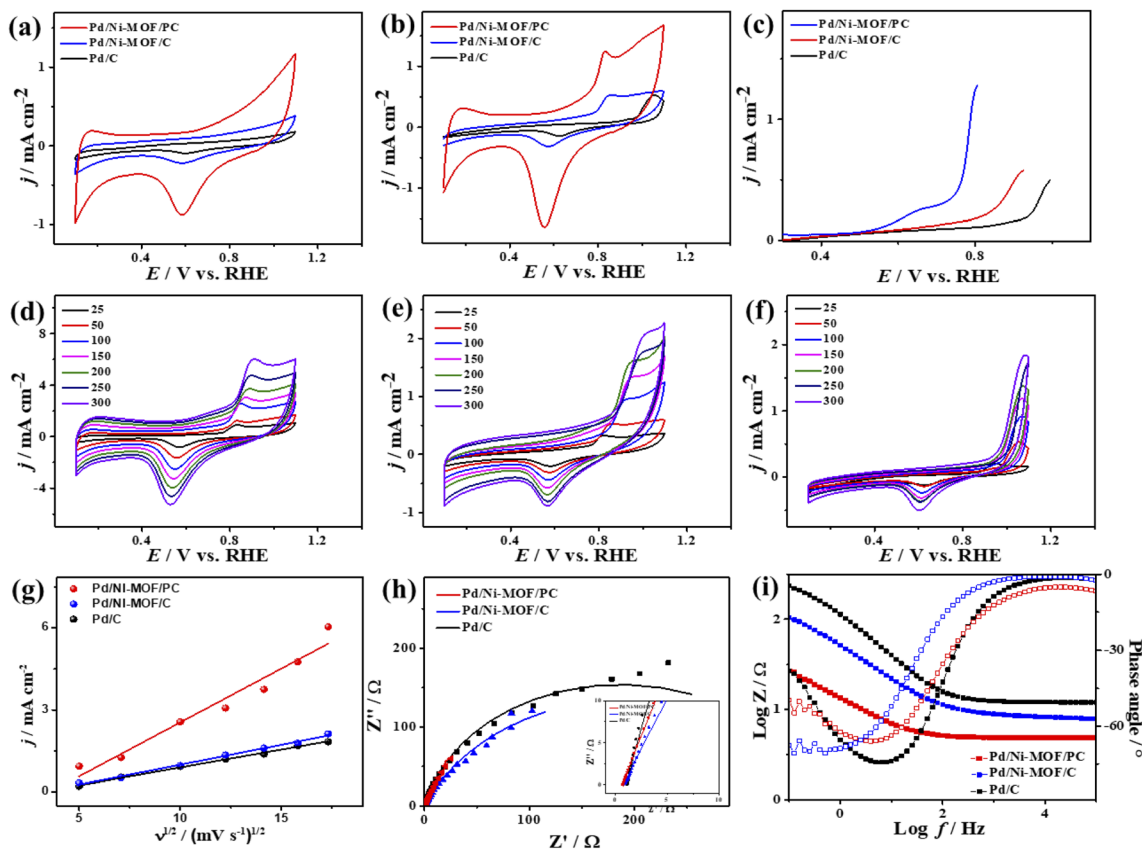


Fig. 7 (a) CV in 0.1 M KOH, (b) CV in CO-saturated 0.1 M NaHCO_3 , and (c) LSV in CO-saturated 0.1 M NaHCO_3 of Pd/Ni-MOF–PC, Pd/Ni-MOF–C, and commercial Pd/C. CV measured in 0.1 M NaHCO_3 at different scan rates of (d) Pd/Ni-MOF/PC, (e) Pd/Ni-MOF/C, and (f) Pd/C and their (g) related plots of current density vs. square root of scan rates, (h) Nyquist plots, and (i) Bode plots measured in CO-saturated 0.1 M NaHCO_3 electrolyte of Pd/Ni-MOF/PC, Pd/Ni-MOF/C and Pd/C.





Fig. 8 (a–c) CV stability of CO oxidation and (d) I_{anode} stability of Pd/Ni-MOF/PC, Pd/Ni-MOF/C, and Pd/C in CO-saturated 0.1 M NaHClO₄ electrolyte.

in the CO-purged 0.1 M NaHCO₃ electrolyte indicate the high durability of Pd/Ni-MOF/PC than Pd/Ni-MOF/C and Pd/C as appeared in the slower current attenuation. The CVs measured after the CA test in the CO-saturated NaHCO₃ electrolyte (Fig. 8a–c) show that all catalysts earmarked their CO oxidation voltammogram features. Pd/Ni-MOF/PC kept 95% of its initial I_{anode} compared to Pd/Ni-MOF/C (90%) and Pd/C (80%), indicating the superior stability of Pd/Ni-MOF/PC (Fig. 8d). These results warrant that the oxidation performance of Pd/Ni-MOF/PC in HClO₄ is superior to that in KOH and NaHCO₃. This is plausibly due to the greater CO-adsorption ability in HClO₄ relative to KOH and NaHCO₃ as obtained from the integration of the anodic peak current (Table S2[†]). The significant enhancement of the CO oxidation performance of Pd/Ni-MOF/PC plausibly originated from the porous 2D morphology and Pd/Ni-N_x active sites.^{38,43–47}

Porous and structure defective MOF/PC is endowed with outstanding rich electron density, higher electrical conductivity, and enhanced charge transfer; meanwhile, multiple pores enhance the adsorption of reactant molecules (*i.e.*, CO and O₂) and facilitate their diffusion to the inner cavities, which are highly stable against agglomeration.^{38,43–47} In addition, the abundant active sites of Pd/Ni-N_x embedded in MOF/PC allow the activation/dissociation of CO and O₂ along with facilitating the generation of oxygen species (*i.e.*, OH) at low overpotentials. Exploring MOF/PC with Pd/Ni-N_x active sites tailors the electrolyte–electrode interaction and charge transfer resistance resulting in dissimilar CO oxidation activity and voltammogram features in different electrolytes.^{66–68}

Conclusion

This study presents the rational synthesis of Pd/Ni-MOF/PC *via* the microwave-irradiation and carbonization at 900 °C, followed by chemical etching. Pd/Ni-MOF/PC comprises porous 2D carbon nanosheets with abundant pores and Pd/Ni-N_x active sites originating from the *in situ* emitted gases from

triethylamine that facilitate the reduction of Ni-impeded MOF to form Ni nanocrystals, while chemical etching allows the partial etching of Ni nanocrystals, which results in the formation of larger pores and more exposed active sites on the deposition of Pd to form Pd/Ni-N_x. These merits endowed the CO oxidation activity substantially more than that of Pd/Ni-MOF/C (with low porosity or less active Pd/Ni-N_x sites formed without etching) and commercial Pt/C catalyst in HClO₄, KOH, and NaHCO₃ electrolytes. Using different electrolytes alters the CO oxidation activity and voltammogram features, but Pd/Ni-MOF/PC was superior to other catalysts, as shown in the high I_{anode} , low E_{oxi} , E_{onset} , and impedance. The CO oxidation activity of Pd/Ni-MOF/PC was in the order of HClO₄ > KOH > NaHCO₃. This study may allow the fabrication of MOF/PC incorporated with various metals for electrochemical CO oxidation.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

This work was supported by the Qatar University High Impact Internal Grant (QUHI-CAM-22/23-550), Qatar National Research Fund (NPRP13D-0117-200095) and NRF/DSI/Wits SARChI Chair in Materials Electrochemistry and Energy Technologies (MEET) (UID No. 132739). The statements made herein are solely the responsibility of the authors. The authors are grateful to the Environmental Science Center (ESC), Qatar University, for the ICP-OES analysis.

References

- 1 F. Wu, K. Eid, A. M. Abdullah, W. Niu, C. Wang, Y. Lan, A. A. Elzatahry and G. Xu, *ACS Appl. Mater. Interfaces*, 2020, **12**, 31309–31318.
- 2 S. Neatu, F. Neatu, M. I. Chirica, I. Borbáth, E. Talas, A. Tompos, S. Somacescu, P. Osiceanu, A. M. Folgado and A. M. Chaparro, *J. Mater. Chem. A*, 2021, **9**, 17065–17128.
- 3 K. Eid, H. Wang, P. He, K. Wang, T. Ahmad, S. M. Alshehri, Y. Yamauchi and L. Wang, *Nanoscale*, 2015, **7**, 16860–16866.
- 4 S. Lu, K. Eid, D. Ge, J. Guo, L. Wang, H. Wang and H. Gu, *Nanoscale*, 2017, **9**, 1033–1039.
- 5 K. Eid, Y. H. Ahmad, S. Y. AlQaradawi and N. K. Allam, *Catal. Sci. Technol.*, 2017, **7**, 2819–2827.
- 6 Q. Lu, J. Li, K. Eid, X. Gu, Z. Wan, W. Li, R. S. Al-Hajri and A. M. Abdullah, *J. Electroanal. Chem.*, 2022, **916**, 116361.
- 7 K. Eid, Y. H. Ahmad, H. Yu, Y. Li, X. Li, S. Y. AlQaradawi, H. Wang and L. Wang, *Nanoscale*, 2017, **9**, 18881–18889.
- 8 M. Tang, S. Zhang and S. Chen, *Chem. Soc. Rev.*, 2022, **51**, 1529–1546.
- 9 K. Eid, M. H. Sliem, H. Al-Kandari, M. A. Sharaf and A. M. Abdullah, *Langmuir*, 2019, **35**, 3421–3431.
- 10 K. Eid, M. H. Sliem and A. M. Abdullah, *Nanoscale*, 2019, **11**, 11755–11764.



- 11 K. Eid, M. H. Sliem, A. S. Eldesoky, H. Al-Kandari and A. M. Abdullah, *Int. J. Hydrogen Energy*, 2019, **44**, 17943–17953.
- 12 K. Eid, M. H. Sliem, K. Jlassi, A. S. Eldesoky, G. G. Abdo, S. Y. Al-Qaradawi, M. A. Sharaf, A. M. Abdullah and A. A. Elzatahry, *Inorg. Chem. Commun.*, 2019, **107**, 107460.
- 13 Z. Huang, K. Teramura, H. Asakura, S. Hosokawa and T. Tanaka, *Chem. Sci.*, 2017, **8**, 5797–5801.
- 14 X. Chen, L. P. Granda-Marulanda, I. T. McCrum and M. Koper, *Nat. Commun.*, 2022, **13**, 1–11.
- 15 C. R. Zanata, A. C. Gaiotti, L. R. Sandim, C. A. Martins, L. M. Pinto, M. J. Giz and G. A. Camara, *J. Electroanal. Chem.*, 2021, **886**, 115149.
- 16 Y. Liu, W. Li, G. Zhao, G. Qin, Y. Li and Y. Liu, *Nanoscale*, 2021, **13**, 3528–3542.
- 17 K. Eid, M. H. Sliem, M. Al-Ejji, A. M. Abdullah, M. Harfouche and R. S. Varma, *ACS Appl. Mater. Interfaces*, 2022, **14**(36), 40749–40760.
- 18 L. Zhuang, Z. Jia, Y. Wang, X. Zhang, S. Wang, J. Song, L. Tian and T. Qi, *Chem. Eng. J.*, 2022, **438**, 135585.
- 19 C. Liu, Y. Shen, J. Zhang, G. Li, X. Zheng, X. Han, L. Xu, S. Zhu, Y. Chen and Y. Deng, *Adv. Energy Mater.*, 2022, **12**, 2103505.
- 20 J. Huang, Q. Liu, Y. Yan, N. Qian, X. Wu, L. Ji, X. Li, J. Li, D. Yang and H. Zhang, *Nanoscale Adv.*, 2022, **4**, 111–116.
- 21 X. Fu, C. Wan, Y. Huang and X. Duan, *Adv. Funct. Mater.*, 2022, **32**, 2106401.
- 22 A. K. Ipadeola, P. V. Mwonga, S. C. Ray, R. R. Maphanga and K. I. Ozoemena, *ChemElectroChem*, 2020, **7**, 4562–4571.
- 23 J. J. Ogada, A. K. Ipadeola, P. V. Mwonga, A. B. Haruna, F. Nichols, S. Chen, H. A. Miller, M. V. Pagliaro, F. Vizza, J. R. Varcoe, D. M. Meira, D. M. Wamwangi and K. I. Ozoemena, *ACS Catal.*, 2022, **12**, 7014–7029.
- 24 W. Huang, X. Kang, C. Xu, J. Zhou, J. Deng, Y. Li and S. Cheng, *Adv. Mater.*, 2018, **30**, 1706962.
- 25 L. Chen, L. Lu, H. Zhu, Y. Chen, Y. Huang, Y. Li and L. Wang, *Nat. Commun.*, 2017, **8**, 1–9.
- 26 D. Liu, Q. Zeng, H. Liu, C. Hu, D. Chen, L. Xu and J. Yang, *Cell Rep. Phys. Sci.*, 2021, **2**, 100357.
- 27 N. Li, W.-Y. Xia, C.-W. Xu and S. Chen, *J. Energy Inst.*, 2017, **90**, 725–733.
- 28 R. Awasthi and R. Singh, *Carbon*, 2013, **51**, 282–289.
- 29 X. Wang, C. Zhang, M. Chi, M. Wei, X. Dong, A. Zhu, Q. Zhang and Q. Liu, *Int. J. Hydrogen Energy*, 2021, **46**, 19129–19139.
- 30 A. Muthurasu, K. Chhetri, B. Dahal and H. Y. Kim, *Nanoscale*, 2022, **14**(17), 6557–6569.
- 31 M. Lu, M. Zhang, J. Liu, Y. Chen, J. P. Liao, M. Y. Yang, Y. P. Cai, S. L. Li and Y. Q. Lan, *Angew. Chem., Int. Ed.*, 2022, **61**, e202200003.
- 32 A. Kumar, S. Sundriyal, C. Goyal, T. Boruah, D. K. Das, G. Yasin, T. A. Nguyen and S. Gautam, *Nanomater. Electroanalysis Micro Nano Technol.*, 2022, pp. 211–237, DOI: [10.1016/B978-0-323-85710-9.00014-9](https://doi.org/10.1016/B978-0-323-85710-9.00014-9).
- 33 Y. Xue, G. Zhao, R. Yang, F. Chu, J. Chen, L. Wang and X. Huang, *Nanoscale*, 2021, **13**, 3911–3936.
- 34 B. Cui and G.-D. Fu, *Nanoscale*, 2022, **14**(5), 1679–1699.
- 35 M. Trivedi, S. Kumar, A. Arora and K. Goyal, *Metal-Organic Frameworks (MOFs) as Catalysts*, Springer, 2022, pp. 369–390, DOI: [10.1007/978-981-16-7959-9_14](https://doi.org/10.1007/978-981-16-7959-9_14).
- 36 H. Sun, B. Yu, X. Pan, X. Zhu and Z. Liu, *Appl. Spectrosc. Rev.*, 2022, **57**, 513–528.
- 37 J. Liu, T. A. Goetjen, Q. Wang, J. G. Knapp, M. C. Wasson, Y. Yang, Z. H. Syed, M. Delferro, J. M. Notestein and O. K. Farha, *Chem. Soc. Rev.*, 2022, **51**, 1045–1097.
- 38 B. Yi, H. Zhao, L. Cao, X. Si, Y. Jiang, P. Cheng, Y. Zuo, Y. Zhang, L. Su and Y. Wang, *Mater. Today Nano*, 2022, **17**, 100158.
- 39 Y. Zhong, Y. Hu, H. Mo, Z. Wu, X. Fu, L. Zhou, H. Liu, L. Li and X. Liu, *Electrochim. Acta*, 2022, **408**, 139935.
- 40 M. Sadakiyo, *Nanoscale*, 2022, **14**, 3398–3406.
- 41 A. K. Ipadeola, P. V. Mwonga, S. C. Ray, R. R. Maphanga and K. I. Ozoemena, *Electroanalysis*, 2020, **32**, 3060–3074.
- 42 T. P. Mofokeng, A. K. Ipadeola, Z. N. Tetana and K. I. Ozoemena, *ACS Omega*, 2020, **5**, 20461–20472.
- 43 F. Abbasi, J. Karimi-Sabet and C. Ghotbi, *Int. J. Hydrogen Energy*, 2021, **46**, 12822–12834.
- 44 Y. Yue, Y. Li, T. Wang, S. Wang, L. Han and C. Du, *Catal. Lett.*, 2022, 1–10.
- 45 R. S. Salama, M. A. Mannaa, H. M. Altass, A. A. Ibrahim and A. E. R. S. Khder, *RSC Adv.*, 2021, **11**, 4318–4326.
- 46 W. Ru, Y. Liu, B. Fu, F. Fu, J. Feng and D. Li, *Small*, 2022, **18**, 2103852.
- 47 Q. Liang, Z. Zhao, J. Liu, Y.-C. Wei, G.-Y. Jiang and A.-J. Duan, *Acta Phys.-Chim. Sin.*, 2014, **30**, 129–134.
- 48 X. Zhang, D. Xue, S. Jiang, H. Xia, Y. Yang, W. Yan, J. Hu and J. Zhang, *InfoMat*, 2022, **4**, e12257.
- 49 M. Baghbanzadeh, L. Carbone, P. D. Cozzoli and C. O. Kappe, *Angew. Chem., Int. Ed.*, 2011, **50**, 11312–11359.
- 50 A. K. Ipadeola, R. Barik, S. C. Ray and K. I. Ozoemena, *Electrocatalysis*, 2019, **10**, 366–380.
- 51 A. K. Ipadeola and K. I. Ozoemena, *RSC Adv.*, 2020, **10**, 17359–17368.
- 52 M. Alle, S. H. Lee and J. C. Kim, *J. Mater. Sci. Technol.*, 2020, **41**, 168–177.
- 53 N. E. Mphahlele, A. K. Ipadeola, A. B. Haruna, P. V. Mwonga, R. M. Modibedi, N. Palaniandy, C. Billing and K. I. Ozoemena, *Electrochim. Acta*, 2022, **409**, 139977.
- 54 Y. Asakuma, S. Matsumura, M. Asada and C. Phan, *Int. J. Thermophys.*, 2018, **39**, 1–12.
- 55 J. Han, G. Yang, H. Ding and X. Chen, *Microporous Mesoporous Mater.*, 2021, **319**, 111067.
- 56 K. Eid, H. Wang, V. Malgras, Z. A. Allothman, Y. Yamauchi and L. Wang, *J. Phys. Chem. C*, 2015, **119**, 19947–19953.
- 57 C. Li, K. Eid, H. Wang, Y. Deng, S. Lu, X. Li, L. Wang and H. Gu, *New J. Chem.*, 2018, **42**, 798–801.
- 58 B. Salah, K. Eid, A. M. Abdelgwad, Y. Ibrahim, A. M. Abdullah, M. K. Hassan and K. I. Ozoemena, *Electroanalysis*, 2022, **34**, 677–683.
- 59 B. Du, S. A. Rabb, C. Zangmeister and Y. Tong, *Phys. Chem. Chem. Phys.*, 2009, **11**, 8231–8239.
- 60 T. Matsui, K. Fujiwara, T. Okanishi, R. Kikuchi, T. Takeguchi and K. Eguchi, *J. Power Sources*, 2006, **155**, 152–156.



- 61 A. K. Ipadeola, P. V. Mwonga and K. I. Ozoemena, *Electrochim. Acta*, 2021, **390**, 138860.
- 62 A. K. Ipadeola, N. Z. Lisa Mathebula, M. V. Pagliaro, H. A. Miller, F. Vizza, V. Davies, Q. Jia, F. Marken and K. I. Ozoemena, *ACS Appl. Energy Mater.*, 2020, **3**, 8786–8802.
- 63 B. N. Grgur, N. M. Marković, C. A. Lucas and P. N. Ross Jr, *J. Serbian Chem. Soc.*, 2001, **66**, 785–797.
- 64 T. Jurzinsky, C. Cremers, K. Pinkwart and J. Tübke, *Electrochim. Acta*, 2016, **199**, 270–279.
- 65 F. Wu, K. Eid, A. M. Abdullah, W. Niu, C. Wang, Y. Lan, A. A. Elzatahry and G. Xu, *ACS Appl. Mater. Interfaces*, 2020, **12**, 31309–31318.
- 66 A. S. Bandarenka, A. S. Varela, M. Karamad, F. Calle-Vallejo, L. Bech, F. J. Perez-Alonso, J. Rossmeisl, I. E. Stephens and I. Chorkendorff, *Angew. Chem., Int. Ed.*, 2012, **124**, 12015–12018.
- 67 C. Dupont, Y. Jugnet and D. Loffreda, *J. Am. Chem. Soc.*, 2006, **128**, 9129–9136.
- 68 A. K. Ipadeola, K. Eid, A. M. Abdullah and K. I. Ozoemena, *Langmuir*, 2022, **38**(36), 11109–11120.

