



Cite this: *Chem. Sci.*, 2022, 13, 5568

All publication charges for this article have been paid for by the Royal Society of Chemistry

A sequential cyclization/ π -extension strategy for modular construction of nanographenes enabled by stannole cycloadditions†

Harrison M. Bergman, ^a D. Dawson Beattie,^a Gavin R. Kiel, ^a Rex C. Handford,^a Yi Liu ^{*b} and T. Don Tilley ^{*a}

The synthesis of polycyclic aromatic hydrocarbons (PAHs) and related nanographenes requires the selective and efficient fusion of multiple aromatic rings. For this purpose, the Diels–Alder cycloaddition has proven especially useful; however, this approach currently faces significant limitations, including the lack of versatile strategies to access annulated dienes, the instability of the most commonly used dienes, and difficulties with aromatization of the [4 + 2] adduct. In this report we address these limitations via the marriage of two powerful cycloaddition strategies. First, a formal Cp₂Zr-mediated [2 + 2 + 1] cycloaddition is used to generate a stannole-annulated PAH. Secondly, the stannoles are employed as diene components in a [4 + 2] cycloaddition/aromatization cascade with an aryne, enabling π -extension to afford a larger PAH. This discovery of stannoles as highly reactive – yet stable for handling – diene equivalents, and the development of a modular strategy for their synthesis, should significantly extend the structural scope of PAHs accessible by a [4 + 2] cycloaddition approach.

Received 21st January 2022

Accepted 29th March 2022

DOI: 10.1039/d2sc00397j

rsc.li/chemical-science

Introduction

Polycyclic aromatic hydrocarbons (PAHs) are a versatile class of organic compounds with diverse applications as components of electronic devices such as OLEDs, OFETs, and OPVs,^{1–3} as well as in biology and medicine.⁴ In general, the utility of these compounds stems from the diverse array of properties that can be synthetically controlled by tuning (for example) molecular shape, edge structure, and functionality.^{5,6} Despite established advances in PAH chemistry, there remain substantial synthetic limitations that restrict possible architectures and new applications.

The main challenge associated with PAH synthesis is the lack of general, reliable methods for the selective fusion of aromatic rings, which generally rely on harsh conditions or specific functional handles to facilitate fusion. Significant effort has gone into developing such strategies,⁷ and several reaction classes have emerged to greatly expand the diversity of accessible PAHs. These include oxidative couplings such as the Scholl reaction, electrophilic cyclization of alkynes,⁸ radical cascades,

annulative π -extension,⁹ transition metal mediated [2 + 2 + n] cycloadditions,^{10–13} and the Diels Alder reaction.¹⁴

The Diels Alder reaction, or [4 + 2] cycloaddition, has attracted particular interest in the synthesis of PAHs due to its versatility and operational simplicity.^{14,15} For this application, dienes capable of undergoing facile aromatization after cycloaddition are necessary, and several systems are commonly employed. Perhaps the most ubiquitous are furans which generate epoxy-bridged intermediates, with aromatization occurring in a second, deoxygenation step (Scheme 1a).


While this method has proven valuable, particularly in the synthesis of sterically crowded acenes known as twistacenes,¹⁶ it suffers from low overall yields and poor functional group tolerance due to the harsh aromatization step. Thus, the development of diene sources that undergo spontaneous aromatization is of high interest. There are three commonly employed dienes of this type: cyclopentadienones,^{17–19} thiophene dioxides,^{20,21} and oxadiazinones.^{22–24} In each case, the cycloaddition intermediate aromatizes with liberation of a gas. Although these examples generate aromatic products in a single step, the electron-withdrawing character of the eliminated substituent (CO, SO₂, and CO₂) causes the dienes to be sluggish partners for standard Diels Alder reactions. This generally corresponds to limited yields for cycloadditions with benzyne, despite their promise as crucial building blocks in syntheses of nanocarbons.

Another significant roadblock in the application of these dienes to nanographene synthesis is the challenge of incorporating them into complex fused ring systems. Annulated furans

^aDepartment of Chemistry, University of California, Berkeley, California 94720, USA. E-mail: tdtalley@berkeley.edu

^bMolecular Foundry, Lawrence Berkeley National Laboratory, Berkeley, California 94720, USA. E-mail: yliu@lbl.gov

† Electronic supplementary information (ESI) available. CCDC 2121655. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d2sc00397j

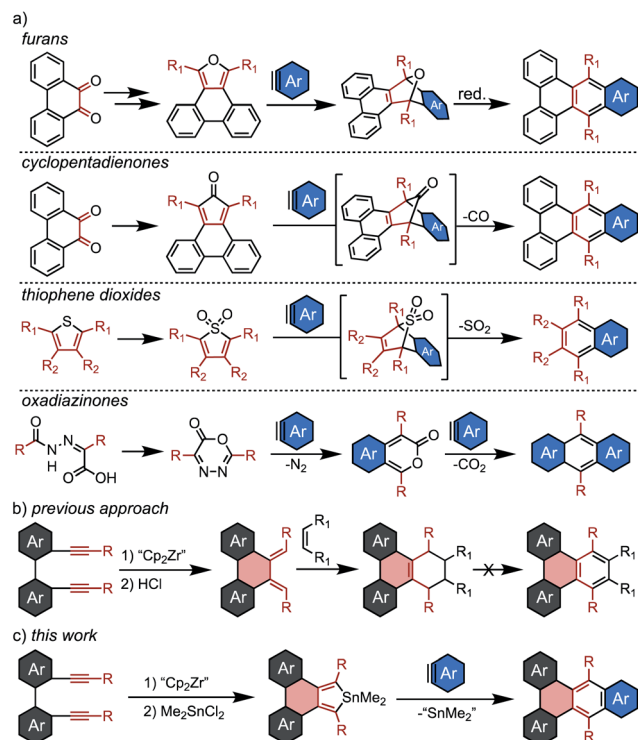

Scheme 1 (a) Commonly employed dienes for the synthesis of nanographenes via [4 + 2] cycloadditions; (b) prior development of a zirconocene coupling approach to the synthesis of PAHs from tethered diynes; (c) this work, combining the zirconocene coupling approach to PAH synthesis with π -extension via the [4 + 2] cycloaddition of stannoles.

and cyclopentadienones are most commonly generated from o-diones, and thus can only be appended to PAHs for which the diones are readily accessible. There are currently no straightforward ways to generate PAH-thiophene dioxides, and oxadiazinones are fundamentally incapable of being annulated to larger fused systems. Thus, the development of new strategies for appending reactive dienes to nanographene cores is critical for expanding the utility of Diels Alder cycloadditions in PAH synthesis.

Previously, this group attempted to resolve this issue *via* the use of a [2 + 2 + 1] zirconocene-mediated coupling of tethered diynes (Scheme 1b).²⁵ This strategy enabled the synthesis of a wide range of nanographenes from unfused precursors, and facile protodemetalation of the resulting zirconacycles generated PAH-appended dienes. Although the dienes were reactive towards dienophiles, aromatization of the resulting cycloaddition products was not possible.

To address this limitation, we sought to develop a new Diels Alder diene source that is broadly reactive with arynes and readily installed into a wide range of complex PAHs *via* the zirconocene coupling approach. To this end, several papers from Hitomi²⁶ and Neumann²⁷ that describe stannoles as sources of stannylene (:SnR₂) upon reaction with dienophiles served as inspiration. Although these studies focused primarily on the liberation of stannylene, they described high yields of the aromatic byproducts, indicating that stannoles not only

undergo efficient [4 + 2] cycloadditions but also spontaneously aromatize upon liberation of divalent tin. Despite a few early observations, stannole cycloaddition chemistry has not been developed into a generally applicable methodology.^{28,29} Although stannoles have been shown to be effective cross-coupling partners for direct annulation *via* Pd catalysis,^{30,31} this is the first report of their general use as efficient dienes for [4 + 2] cycloadditions to generate π -extended polycyclic aromatic hydrocarbons.

In this contribution, stannoles are shown to be readily incorporated into a wide range of PAH structures using the zirconocene coupling of tethered diynes. These stannoles then serve as highly efficient dienes in Diels Alder cycloadditions with arynes (Scheme 1c), most strikingly from *ortho*-dihalo substrates which are generally incompatible with other spontaneously aromatizing dienes. Furthermore, in a demonstration of the potential for stannoles to engage in a more diverse array of cycloaddition reactions, one example is shown to undergo an unusual dimerization at high temperatures to generate a helically chiral, 1,2,4,5-cyclooctatetraene in exceptional yield ($\geq 95\%$).

Results and discussion


It seemed that stannoles could be appended to PAHs *via* zirconocene coupling of tethered alkynes, followed by transmetalation to the stannole *via* the CuCl-mediated conditions developed by Takahashi.³² This strategy was initially tested on **1a** to confirm that the reaction conditions were effective for previously unexplored tethered diynes (Scheme 2). It was determined that the sequence can either be performed in a stepwise manner through isolation of the intermediate zirconacycle, or in a convenient one-pot procedure using the Negishi protocol in essentially the same yield (see page S7† for all reported preparations).

Beyond the model stannole **2a**, it is possible to construct more complex stannole-containing PAHs using this methodology (Scheme 2). Zirconocene coupling of alkynes may also be used to generate PAHs containing 5-member rings, which can similarly undergo transmetalation to stannoles as evidenced by the synthesis of stannole **2b** in 73% yield. The efficiency of stannole formation makes it possible to synthesize bis- and tris-stannoles in good yield, which enables the construction of more complex diene-containing PAH architectures such as **2c–2e**, which would be difficult to access by established methods.

Compound **2a** was utilized as a model system to explore the reactivity of stannoles for [4 + 2] cycloadditions with benzyne, beginning with the widely used and mild benzyne precursor 2-(Me₃Si)C₆H₄(OTf). Initially, simple mixing of **2a**, the benzyne precursor, and the soluble fluoride source [nBu₄N][Ph₃SiF₂] in toluene furnished **3a** in 78% yield by ¹H NMR spectroscopy after some optimization (page S18†). A significant improvement to 88% was seen upon addition of dimethylacetylenedicarboxylate (DMAD) as a stannylene trap,²⁵ but no other commonly employed traps were effective (diphenyl disulfide, diacetyl, butylbromide).

Although *ortho*-dihalo precursors to arynes generally require harsher reaction conditions, they are highly valuable building



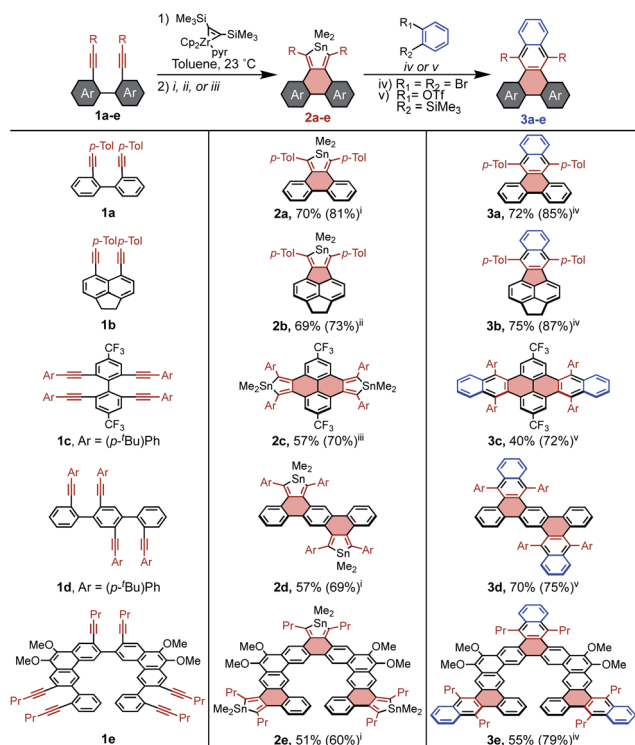


Scheme 2 Substrate scope of stannole synthesis and subsequent π -extension via [4 + 2] cycloaddition with benzyne. For **2a–2e**, yields represent total isolated yield across two steps from the diyne, while yields from isolated zirconacycles are given in parenthesis. For **3a–3e**, *in situ* yields as determined by ^1H NMR spectroscopy are given in parenthesis. Reagents and conditions: (i) Me_2SnCl_2 , CuCl, LiCl, toluene, 23 $^\circ\text{C}$; (ii) Me_2SnCl_2 , CuCl, LiCl, toluene, 60 $^\circ\text{C}$; (iii) Me_2SnCl_2 , CuCl, ZnCl₂, toluene, 23 $^\circ\text{C}$; (iv) 1,2-dibromobenzene (1.2 equiv.), $^n\text{BuLi}$ (1.1 equiv.), toluene, 23 $^\circ\text{C}$; (v) 2-(Me_3Si) $\text{C}_6\text{H}_4(\text{OTf})$ (1.1 equiv.), $[\text{NBu}_4]\text{Ph}_3\text{SiF}_2$ (3.3 equiv.), dimethylacetylenedicarboxylate (1.5 equiv.), toluene, 60 $^\circ\text{C}$.

blocks due to their availability. Significantly, stannoles are robust in the presence of $^n\text{BuLi}$, and treatment of *o*-dibromobenzene with $^n\text{BuLi}$ at 23 $^\circ\text{C}$ in the presence of stannole **2a** resulted in the formation of **3a** in 85% yield. This efficient transformation contrasts with the absence of analogous reactions involving cyclopentadienones, thiophene dioxides, and pyrones, which are ostensibly reactive toward organolithium species.

Generalization of these cycloaddition conditions to stannoles **2b–2e** enabled facile access to π -extended PAHs **3b–3e**. In each case except **2d**, stannoles were compatible with both types of benzyne precursors, and the method that resulted in the higher isolated yield is reported in Scheme 2. It is believed that the reaction of **2d** with *o*-dibromobenzene failed due to its very limited solubility in aromatic solvents, making its reaction with the generated benzyne too sluggish to compete with benzyne decomposition.

The range of additional benzyne sources that are compatible with [4 + 2] cycloadditions to stannoles was further explored using **2a** as a model system. For the *ortho*- $\text{Me}_3\text{Si-OTf}$ derivative of naphthalene, the cycloaddition product **4** was accessed in 85% yield, suggesting the generality of these conditions to other

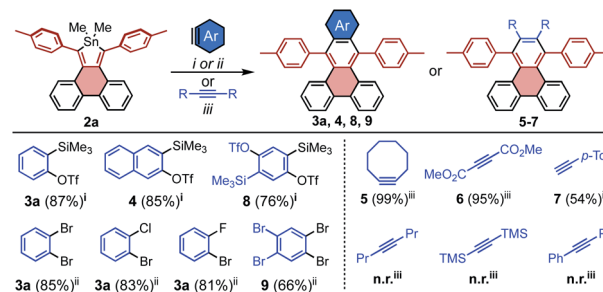


Scheme 3 Benzyne and alkyne substrate scope for [4 + 2] cycloadditions with model stannole system **2a**. Given yields were determined *in situ* via ^1H NMR spectroscopy. Reagents and conditions: (i) aryne (1.1 equiv.), $[\text{NBu}_4\text{N}][\text{Ph}_3\text{SiF}_2]$ (3 equiv.), dimethylacetylenedicarboxylate (1.5 equiv.), toluene, 60 $^\circ\text{C}$; (ii) aryne (1.2 equiv.), $^n\text{BuLi}$ (1.1 equiv.), toluene, 23 $^\circ\text{C}$; (iii) alkyne (2.5 equiv.), toluene, 100–160 $^\circ\text{C}$.

ortho- $\text{Me}_3\text{Si-OTf}$ PAHs. Other dihalo reactant partners may be employed, as observed for 2-chloro and 2-fluorobromobenzene which both gave **3a** in greater than 80% yield (Scheme 3).

Reactions of stannoles with common alkynes were also explored. Generally, **2a** reacted rapidly and efficiently at moderate temperatures with activated internal alkynes such as strained cyclooctyne and electron-deficient dimethylacetylene dicarboxylate, to furnish **5** and **6** in 99% and 95% yields, respectively. The unactivated terminal alkyne 4-ethynyl toluene required elevated temperature but gave reasonable conversion to the unsymmetrical PAH **7** in 54% yield (Scheme 3, R,R = H, *p*-Tol). The unactivated internal alkynes 4-octyne, bis(trimethylsilyl)acetylene, and diphenyl acetylene were generally unreactive, even at highly elevated temperatures (160 $^\circ\text{C}$ in mesitylene).

The efficiency with which stannoles undergo cycloadditions with aryne makes them desirable substrates for the synthesis of extended π -systems through multiple, successive cycloadditions. To this end, conditions were developed for the iterative addition of stannoles to bifunctional aryne precursors. Stannole

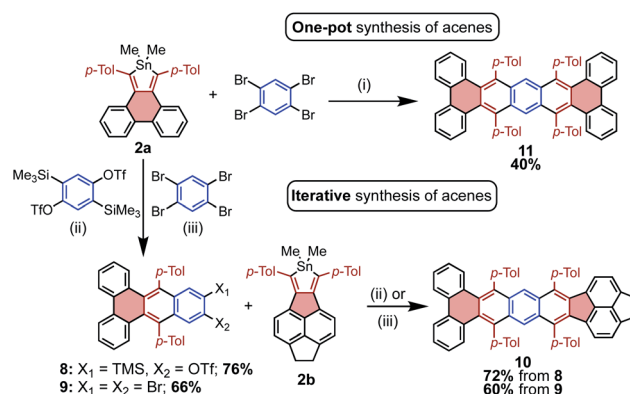

Scheme 4 Synthesis of acenes via the multiple addition of stannoles to benzyne. Reagents and conditions: (i) aryne (0.5 equiv.), $^n\text{BuLi}$ (1.1 equiv.), toluene, 23 $^\circ\text{C}$; (ii) aryne (1.1 equiv.), $[\text{NBu}_4\text{N}][\text{Ph}_3\text{SiF}_2]$ (3 equiv.), DMAD (1.5 equiv.), toluene, 60 $^\circ\text{C}$; (iii) aryne (2 equiv.), $^n\text{BuLi}$ (1.1 equiv.), toluene, 23 $^\circ\text{C}$.




2a was treated with 1.1 equivs of a bis-benzynes precursor under standard conditions for $\text{Me}_3\text{Si-OTf}$ precursors, and this afforded the desired mono-addition product **8** in 76% isolated yield (Scheme 3). A larger excess of the aryne precursor (2 equiv.) increased the yield of **8** to 85% (see page S13†). Similarly, treatment of stannole **2a** with an excess of 1,2,4,5-tetrabromobenzene (2 equiv.) and $^n\text{BuLi}$ (1.1 equiv.) afforded the mono-addition product **9** in 66% isolated yield. Both **8** and **9** participated in a second cycloaddition with stannole **2b** to give unsymmetrical acene **10** in 72 and 60% yields, respectively (Scheme 4). One-pot double-addition of stannole **2a** to 0.5 equivalents of 1,2,4,5-tetrabromobenzene was also successful, to generate tetrabenzopentacene **11** in 40% yield.

To further explore possibilities for this cycloaddition chemistry in producing unusual PAH structures, the molecular “lobster-shaped” compound **12** was chosen as a target that would be difficult to obtain using other methodologies (Scheme 5). Compound **12** was generated from stannole **2e** and benzyne precursor **9** in a manner similar to that previously described; however, due to the insolubility of **9**, 1-chloronaphthalene was used as a solvent to fully solubilize both components prior to benzyne formation. From these conditions, **12** was isolated in 27% yield, indicating an efficiency of approximately 65% per cycloaddition. Compound **12** displayed a propensity to aggregate in solution, producing sharp resonances in ^1H NMR spectra only at concentrations below 0.4 mM. This is likely a function of the significant π -extension in this molecule, as similar compound **3e** does not display this behavior in solution. This aggregation behavior complicates assessment of purity for **12**, as the isolated material still displays some broad resonances in addition to sharp peaks associated with unaggregated **11** (by ^1H NMR spectroscopy). The broad resonances may be due to impurities or


partial aggregation. Despite this, MALDI unambiguously confirms the presence of **12**, and does not display peaks corresponding to over- or under-substitution in the range of 500–3000 amu (Fig. S54†). This suggests that the broadness observed by ^1H NMR spectroscopy is likely due to aggregation rather than the presence of major impurities.

Given the facile elimination of divalent tin during the cycloadditions described above, it seemed possible that stannoles might undergo other cycloaddition–elimination processes. To explore the possibility of dimerization *via* cycloaddition, stannole **2a** was heated to 160 °C in toluene- d_8 in a sealed reaction vessel and the reaction mixture was monitored by ^1H NMR spectroscopy. Over a period of 12 h a new species formed in exceptionally high yield (>95%) displaying 4 tolyl CH_3 resonances of equal intensity and lacking any discernible resonances from dimethyltin. This is consistent with a product that is a highly unsymmetrical dimer, formed by elimination of Me_2Sn . Single crystals of the product were grown by slow diffusion of hexanes into a concentrated sample in CDCl_3 , and X-ray crystallography confirmed the product as compound **13**, a helically chiral 1,2,4,5-cyclooctatetraene (COT) (Scheme 6). While there is a literature report of a COT with this substitution pattern,³³ it was formed as a minor product; to our knowledge, this is the first observation of a high-yield, selective synthesis of this type of substituted COT. This result highlights the potential for stannoles as versatile diene sources for a range of cycloadditions, making them valuable divergent building blocks for the synthesis of conjugated molecules.

The photophysics of **3b–3e**, **4**, **11**, and **12** were investigated by UV-vis and fluorescence spectroscopy (Fig. 1). The fine structure in the absorbance spectra displays significant sensitivity to the pattern of ring fusion, with **3c–3e** displaying different relative intensities of the three main absorption bands. However, the absorption onset ($\lambda_{\text{abs}}^{\text{onset}}$), and consequently the optical HOMO–LUMO gap (E_{opt}), are fairly consistent for the series at 3.03, 2.90, and 2.90 eV respectively (Table 1). The incorporation of a five-member ring into **3b** significantly alters the shape of the absorption spectrum, and imbues the structure with a notably smaller E_{opt} of 2.86 eV than **3a** despite their similarly sized π -system. Increasing the length of the acene fragment in these systems bathochromically shifts the absorption onset and decreases the HOMO–LUMO gap, with dibenzotetracene **4** reaching 2.70 eV, and tetrabenzopentacenes **11** and **12** reaching 2.35 and 2.38 eV respectively. The fluorescence spectra of the six fully benzenoid structures display similar shapes with two broad peaks, while **3b** displays three. The trends in fluorescence maximum ($\lambda_{\text{em}}^{\text{max}}$) mirror those in absorption onset, with **3c–3e** displaying highly similar maxima at 434, 435, and 451 nm

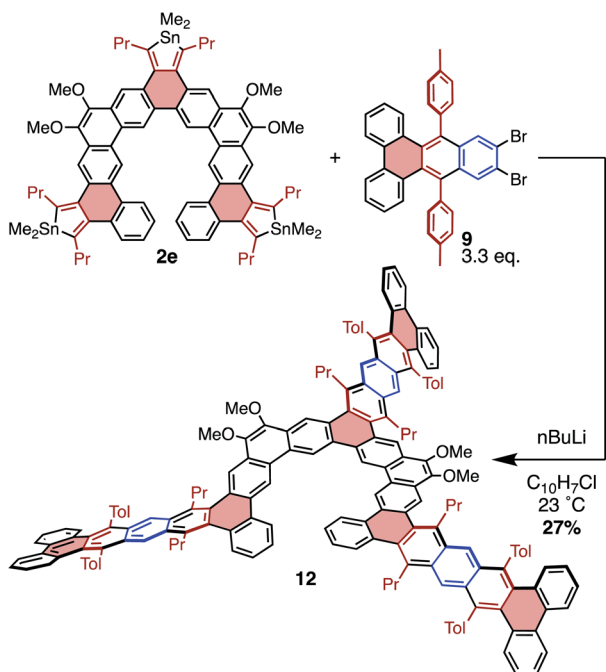

Scheme 5 Synthesis of a π -extended helicene.

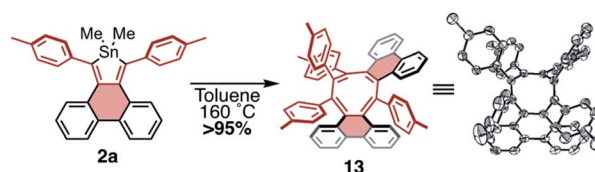

Scheme 6 Formal [4 + 4] dimerization of stannoles to generate a helically chiral cyclooctatetraene.



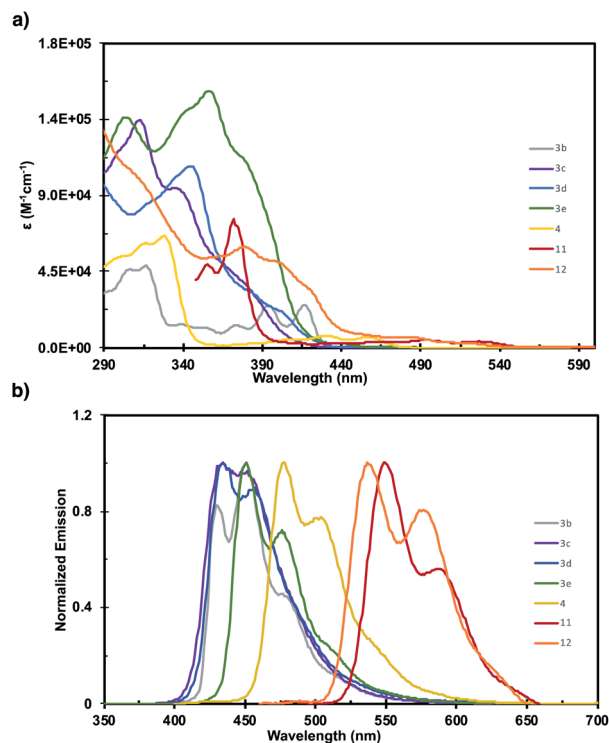


Fig. 1 Steady-state photophysics of **3b** (gray), **3c** (purple), **3d** (blue), **3e** (green), **4** (yellow), **11** (red), and **12** (orange). (a) UV-vis and (b) fluorescence spectroscopy acquired at 5×10^{-6} M in THF (**3b**, **3c**, **3d**, **3e**, **4**, **12**) and 1-chloronaphthalene (**11**). All fluorescence spectra were normalized to their respective λ_{max} .

Table 1 Summary of photophysical properties of key PAHs

Compound	$\lambda_{\text{abs}}^{\text{max}}$ (nm)	$\lambda_{\text{abs}}^{\text{onset}}$ (nm)	$\lambda_{\text{em}}^{\text{max}}$ (nm)	E_{opt} (eV)
3b	316	434	451	2.86
3c	312	409	434	3.03
3d	344	428	435	2.90
3e	357	428	451	2.90
4	327	459	477	2.70
11	372	527	551	2.35
12	308	521	538	2.38

respectively. **4**, **11**, and **12** are notably bathochromically shifted to 477, 551, and 538 nm respectively. These results highlight how orthogonal synthetic control over the core pattern of ring-fusion and the degree of π -extension enables tuning key aspects of the photophysical properties such as fine structure, HOMO–LUMO gap, and fluorescence.

Conclusions

In conclusion, stannoles represent a versatile diene source in $[4 + 2]$ cycloadditions for the synthesis of π -extended aromatic systems. The high yielding cycloaddition–aromatization cascade and the broad compatibility with arynes suggest that stannoles can be superior to commonly employed cyclopentadienones for many applications in PAH synthesis, and their generation *via* $[2 + 2 + 1]$ cycloadditions provides a complimentary approach to established

methods for use of reactive dienes in the expansion of diverse PAH cores. Additionally, the high-yield formation of COT derivative **13** suggests that stannoles may be useful synthons for cycloadditions beyond $[4 + 2]$, where their spontaneous aromatization is highly desirable for the synthesis of unusual conjugated ring structures.

Data availability

Crystallographic data for **13** has been deposited at the CCDC under 2121655.

Author contributions

H. M. B. and T. D. T. conceived of the idea. H. M. B. developed the methodology. D. D. B. expanded the methodology and substrate scope. H. M. B., D. D. B., and G. R. K. acquired the data for synthesis and characterization. R. C. H. acquired and analysed the crystallographic data for compound **13**. H. M. B., D. D. B., Y. L., and T. D. T. wrote and edited the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was funded by the National Science Foundation under Grant No. CHE-2103696. Work performed at the Molecular Foundry was supported by the Office of Science, Office of Basic Energy Sciences, of the US Department of Energy under Contract No. DE-AC02-05CH11231. The authors thank Dr Hasan Celik for assistance with NMR spectroscopy and Justin Jurczyk for useful discussions. Crystallographic analysis was performed at UC Berkeley CheXray facility, which is supported by the NIH Shared Instrumentation Grant S10-RR027172.

Notes and references

- S. Günes, H. Neugebauer and N. S. Sariciftci, Conjugated Polymer-Based Organic Solar Cells, *Chem. Rev.*, 2007, **107**, 1324–1338, DOI: 10.1021/cr050149z.
- T. M. Figueira-Duarte and K. Mullen, Pyrene-Based Materials for Organic Electronics, *Chem. Rev.*, 2011, **111**, 7260–7314, DOI: 10.1021/cr100428a.
- J. Wu, W. Pisula and K. Müllen, Graphenes as Potential Material for Electronics, *Chem. Rev.*, 2007, **107**, 718–747, DOI: 10.1021/cr068010r.
- N. Panwar, A. M. Soehartono, K. K. Chan, S. Zeng, G. Xu, J. Qu, P. Coquet, K. T. Yong and X. Chen, Nanocarbons for Biology and Medicine: Sensing, Imaging, and Drug Delivery, *Chem. Rev.*, 2019, **119**, 9559–9656, DOI: 10.1021/acs.chemrev.9b00099.
- Z. Sun and J. Wu, Open-Shell Polycyclic Aromatic Hydrocarbons, *J. Mater. Chem.*, 2012, **22**, 4151–4160, DOI: 10.1039/c1jm14786b.
- J. Wu and K. Müllen, All-Benzenoid Polycyclic Aromatic Hydrocarbons: Synthesis, Self-Assembly and Applications



- in Organic Electronics, *Carbon-Rich Compounds: From Molecules to Materials*, John Wiley and Sons, 2006, pp. 90–139, DOI: 10.1002/3527607994.ch3.
- 7 A. Narita, X. Y. Wang, X. Feng and K. Müllen, New Advances in Nanographene Chemistry, *Chem. Soc. Rev.*, 2015, **44**, 6616–6643, DOI: 10.1039/c5cs00183h.
 - 8 M. B. Goldfinger, K. B. Crawford and T. M. Swager, Directed Electrophilic Cyclizations: Efficient Methodology for the Synthesis of Fused Polycyclic Aromatics, *J. Am. Chem. Soc.*, 1997, **119**, 4578–4593, DOI: 10.1021/ja9642673.
 - 9 H. Ito, Y. Segawa, K. Murakami and K. Itami, Polycyclic Arene Synthesis by Annulative π -Extension, *J. Am. Chem. Soc.*, 2019, **141**, 3–10, DOI: 10.1021/jacs.8b09232.
 - 10 K. P. C. Vollhardt, Cobalt-Mediated [2 + 2 + 2]-Cycloadditions: A Maturing Synthetic Strategy [New Synthetic Methods (43)], *Angew. Chem., Int. Ed.*, 1984, **23**, 539–556, DOI: 10.1002/anie.198405393.
 - 11 S. Han, A. D. Bond, R. L. Disch, D. Holmes, J. M. Schulman, S. J. Teat, K. P. C. Vollhardt and G. D. Whitener, Total Syntheses and Structures of Angular [6]- and [7]Phenylene: The First Helical Phenylenes (Heliphenes), *Angew. Chem., Int. Ed.*, 2002, **41**, 3223–3227, DOI: 10.1002/1521-3773(20020902)41:17<3223::AID-ANIE3223>3.0.CO;2-G.
 - 12 T. Jin, J. Zhao, N. Asao and Y. Yamamoto, Metal-Catalyzed Annulation Reactions for π -Conjugated Polycycles, *Chem.–Eur. J.*, 2014, **20**, 3554–3576, DOI: 10.1002/chem.201304640.
 - 13 F. Teplý, I. G. Stará, I. Starý, A. Kollárovič, D. Šaman, L. Rulíšek and P. Fiedler, Synthesis of [5]-, [6]-, and [7] Helicene *via* Ni(0)- or Co(I)-Catalyzed Isomerization of Aromatic Cis,Cis-Dienetriynes, *J. Am. Chem. Soc.*, 2002, **124**, 9175–9180, DOI: 10.1021/ja0259584.
 - 14 D. Pérez, D. Peña and E. Guitián, Aryne Cycloaddition Reactions in the Synthesis of Large Polycyclic Aromatic Compounds, *Eur. J. Org. Chem.*, 2013, **2013**, 5981–6013, DOI: 10.1002/ejoc.201300470.
 - 15 O. T. Dyan, G. I. Borodkin and P. A. Zaikin, The Diels–Alder Reaction for the Synthesis of Polycyclic Aromatic Compounds, *Eur. J. Org. Chem.*, 2019, 7271–7306, DOI: 10.1002/ejoc.201901254.
 - 16 Y. Xiao, J. T. Mague, R. H. Schmehl, F. M. Haque and R. A. Pascal, Dodecaphenyltetracene, *Angew. Chem., Int. Ed.*, 2019, **58**, 2831–2833, DOI: 10.1002/anie.201812418.
 - 17 R. G. Clevenger, B. Kumar, E. M. Menuet and K. V. Kilway, Synthesis and Structure of a Longitudinally Twisted Hexacene, *Chem.–Eur. J.*, 2018, **24**, 3113–3116, DOI: 10.1002/chem.201705676.
 - 18 H. M. Duong, M. Bendikov, D. Steiger, Q. Zhang, G. Sonmez, J. Yamada and F. Wudl, Efficient Synthesis of a Novel, Twisted and Stable, Electroluminescent “Twistacene”, *Org. Lett.*, 2003, **5**, 4433–4436, DOI: 10.1021/OL035751V.
 - 19 X. Qiao, M. A. Padula, D. M. Ho, N. J. Vogelaar, C. E. Schutt and R. A. Pascal, Octaphenylanthracene and Decaphenylanthracene, *J. Am. Chem. Soc.*, 1996, **118**, 741–745, DOI: 10.1021/ja953669s.
 - 20 J. W. Barton, M. K. Shepherd and R. J. Willis, Polycyclic Biphenylenes. Part 6. Direct Routes to Benzo[b] Biphenylene and Related Systems *via* Cycloaddition Reactions, *J. Chem. Soc., Perkin Trans. 1*, 1986, 967–971, DOI: 10.1039/p19860000967.
 - 21 J. Nakayama, S. Yamaoka, T. Nakanishi and M. Hoshino, 3,4-Di-*Tert*-Butylthiophene 1,1-Dioxide, a Convenient Precursor of *o*-Di-*Tert*-Butylbenzene and Its Derivatives, *J. Am. Chem. Soc.*, 1988, **110**, 6598–6599, DOI: 10.1021/ja00227a069.
 - 22 Q. Miao, X. Chi, S. Xiao, R. Zeis, M. Lefenfeld, T. Siegrist, M. L. Steigerwald and C. Nuckolls, Organization of Acenes with a Cruciform Assembly Motif, *J. Am. Chem. Soc.*, 2006, **128**, 1340–1345, DOI: 10.1021/ja0570786.
 - 23 W. Steglich, E. Bochmann, G. Gansin and L. Wilschitz, Herstellung Und Reaktionen von 2,5-Diphenyl-6-Oxo-1,3,4-Oxadiazin, *Synthesis*, 1977, **04**, 252–253, DOI: 10.1055/s-1977-24339.
 - 24 M. Ramirez, E. Darzi, J. Donaldson, K. N. Houk and N. K. Garg, Cycloaddition Cascades of Strained Alkynes and Oxadiazinones, *Angew. Chem., Int. Ed.*, 2021, **60**, 18201, DOI: 10.1002/anie.202105244.
 - 25 G. R. Kiel, M. S. Ziegler and T. D. Tilley, Zirconacyclopentadiene-Annulated Polycyclic Aromatic Hydrocarbons, *Angew. Chem., Int. Ed.*, 2017, **56**, 4839–4844, DOI: 10.1002/anie.201700818.
 - 26 K. Kunō, K. Kobayashi, M. Kawanisi, S. Kozima and T. Hitomi, Diorganostannylenes. III. Formation of Dimethylstannylene from 1,1-Dimethyl-2,3,4,5-Tetraphenyl-1-Stannacyclopentadiene and Acetylenes, *J. Organomet. Chem.*, 1977, **137**, 349–354, DOI: 10.1016/S0022-328X(00)81441-2.
 - 27 C. Grugel, W. P. Neumann and M. Schriewer, The First Stable Derivative of 7-Stannanorbornane and Its Thermolysis, *Angew. Chem., Int. Ed.*, 1979, **18**, 543–544, DOI: 10.1002/anie.197905431.
 - 28 B. Wrackmeyer and U. Klaus, New Phosphabenzene by [4 + 2] Cycloaddition of Stannoles to 1-phospha-1-alkynes – Determination of Signs of Coupling Constants $^nJ(^{31}\text{P}, ^{13}\text{C})$, $^nJ(^{31}\text{P}, ^1\text{H})$, $^2J(^{31}\text{P}, ^{29}\text{Si})$, $^2J(^{119}\text{Sn}, ^{31}\text{P})$, *J. Organomet. Chem.*, 1996, **520**, 211–226, DOI: 10.1016/0022-328X(96)06316-4.
 - 29 K. Yoshio, S. Akio, K. Shintaro, C. Kazumi and A. Wataru, Zirconocene Coupling Route to 1,2-disilacyclobutanes, *Chem. Lett.*, 2000, **29**, 1082–1083, DOI: 10.1246/cl.2000.1082.
 - 30 W. Yue, J. Gao, Y. Li, W. Jiang, S. Di Motta, F. Negri and Z. Wang, One-Pot Synthesis of Stable NIR Tetracene Diimides *via* Double Cross-Coupling, *J. Am. Chem. Soc.*, 2011, **133**, 18054–18057, DOI: 10.1021/ja207630a.
 - 31 I. Nagao, M. Shimizu and T. Hiyama, 9-Stannafluorenes: 1,4-Dimetal Equivalents for Aromatic Annulation by Double Cross-Coupling, *Angew. Chem., Int. Ed.*, 2009, **48**, 7573–7576, DOI: 10.1002/anie.200903779.
 - 32 Y. Ura, Y. Li, Z. Xi and T. Takahashi, Cu(I) Catalyzed or Promoted Metallacycle Transfer of Zirconacycles to Stannacycles, *Tetrahedron Lett.*, 1998, **39**, 2787–2790, DOI: 10.1016/S0040-4039(98)00430-4.
 - 33 J. Kubitschke, H. Hopf, P. G. Jones, I. Dix and L. Ernst, A Cyclobutadiene Intermediate in the Intramolecular Cycloaddition of 4,15-Bis(Phenylethynyl)[2.2] Paracyclophane, *Eur. J. Org. Chem.*, 2008, 548–554, DOI: 10.1002/EJOC.200700702.

