# Materials Advances



PAPER View Article Online
View Journal | View Issue



Cite this: *Mater. Adv.*, 2023, 4, 3055

Received 7th May 2023, Accepted 16th June 2023

DOI: 10.1039/d3ma00218g

rsc.li/materials-advances

# Pore volume regulated CO<sub>2</sub> adsorption in C-C bonded porous organic frameworks†

Himan Dev Singh, Deiyush Singh, Deepak Rase and Ramanathan Vaidhyanathan \*\*D\*\*

Three C–C bonded porous organic polymers are assembled by reacting rigid monomers (triformylphenol, triformylphloroglucinol, triformylresorcinol) with pyrrole in a catalyst-free solvothermal reaction. The resulting black-colored amorphous polymers yield moderate Brunauer–Emmett–Teller surface areas (213 m² g $^{-1}$  to 277 m² g $^{-1}$ ). All the polymers exhibit the same pore size but different pore volumes. The impact of pore volume on the adsorption capacity has been investigated. The POFs show excellent CO<sub>2</sub> adsorption properties with moderate heat of adsorption values (31.9–37.6 kJ mol $^{-1}$ ) and good IAST selectivity for CO<sub>2</sub>/N<sub>2</sub> and CO<sub>2</sub>/CH<sub>4</sub> separation. The working capacity of the POFs determined using mixed gas IAST calculations shows that these POFs can preferentially adsorb CO<sub>2</sub> from the CO<sub>2</sub>/N<sub>2</sub> gas mixture. POFs show facile adsorption kinetics with a self-diffusion coefficient on the order of  $10^{-9}$  m² sec $^{-1}$ . The POFs offer excellent stability under acidic conditions and retain their working capacity after long humidity exposure. The stability of POFs under harsh acidic conditions has also been established by 273 K CO<sub>2</sub> adsorption, which shows a negligible fall in the CO<sub>2</sub> saturation capacity.

# Introduction

The increasing atmospheric carbon dioxide concentrations due to anthropogenic emissions is a major environmental concern.<sup>1</sup> The current level of CO2 has increased to 420 ppm and is responsible for global warming.<sup>2</sup> Hence strategies to mitigate CO<sub>2</sub> emissions are urgently needed. A desirable way to reduce carbon dioxide emissions into the environment is by capturing and storing carbon dioxide (CCS) from coal and gas-burning power stations.<sup>3</sup> However, the large energy penalty in the capture process has limited the growth of CCS. The energy input necessary for the regeneration of the material is the primary cause of the high cost.3 For instance, the traditional CO<sub>2</sub> capture method based on alkanolamine solutions produces an energy cost of about 30% of the power plant's output. To tackle this, creating new generation CO<sub>2</sub> capture materials by fine-tuning the thermodynamics of the interaction between CO<sub>2</sub> and the adsorbent is a worthy pursuit.4

In this regard, porous materials have drawn interest from academia and industry across many scientific fields and have shown great promise. Porous organic frameworks (POFs) are an important class of porous materials constructed from lightweight

Department of Chemistry and Centre for Energy Science, Indian Institute of Science Education and Research, Dr Homi Bhabha road, Pashan, Pune, Pune 411008, India. E-mail: vaidhya@iiserpune.ac.in

† Electronic supplementary information (ESI) available. See DOI: https://doi.org/10.1039/d3ma00218g

elements linked by strong covalent bonds that show great potential in a wide range of applications, such as gas storage and separation,  $^{1,5-15}$  catalysis,  $^{16,17}$  chemical sensing,  $^{18,19}$  optoelectronics,  $^{20,21}$  and energy storage.  $^{22,23}$  They have shown great promise due to their low density, high porosity, exceptional thermal and chemical stability, tunable pore size, control of the number of functional groups, *etc.* Along with high porosity, the presence of heteroatoms plays a crucial role in high and selective  $CO_2$  capture; the heteroatoms, especially nitrogen, are known to interact with  $CO_2$  *via* dipole–quadrupole interactions, which is why a lot of work has been carried out on amine grafting and amine impregnation to boost the  $CO_2$  capture performance.  $^{24,25}$ 

High  $CO_2$  uptake, working capacity and selectivity over other gases (particularly  $CO_2/N_2$  selectivity) under humid conditions, fast adsorption kinetics, cheap production cost, and low energy consumption during adsorption and regeneration phases are crucial requirements that must be met by an effective adsorbent. While constructing a sorbent for  $CO_2$  separation, microstructural qualities such the surface area, pore volume, and pore size must be carefully taken into account in addition to surface functionalization and properties of the gas. Materials with pore sizes close to the kinetic diameter of the gas (3.3 Å  $CO_2$ , 3.8 Å of  $CH_4$  and 3.64 Å of  $N_2$ ) would be more suitable due to the possibility of multiple gas—surface interactions. However, the correlation between pore volume and  $CO_2$  capacity is less explored and is relevant to porous polymers. On the surface interaction is a supplementation of the gas and supplementation is relevant to porous polymers.

In 2008, Thomas et al. reported the trimerization of aromatic nitriles (Covalent Triazine Frameworks). They gained much

conditions.<sup>37</sup>

attention due to their conjugated nature, high heteroatom content and surface areas.31 CTF-0, an exceptionally stable POF with a high surface area of 2011 m<sup>2</sup> g<sup>-1</sup> with increased mesoporosity and depleted nitrogen content was synthesized, resulting in a CO<sub>2</sub> uptake capacity of 4.22 mmol g<sup>-1</sup> at 273 K, 1 bar.<sup>32</sup> Dai and coworkers introduced methoxy groups onto a hexaazatriphenylene precursor, enabling CO2 uptake capacity of 6.3 mmol g<sup>-1</sup> at 273 K, 1 bar with a BET surface area of 1090 m<sup>2</sup> g<sup>-1</sup>.<sup>33</sup> Yavuz and coworkers prepared an amide-linked polymer through the polymerization of melamine with a triacid chloride and noticed that the choice of solvents has a significant impact on the morphology of the polymers and, consequently, their capacity to absorb CO<sub>2</sub>. 34 Wang et al. exploited aldehyde-terminated precursors and reacted with pyrrole to obtain NH-rich POFs. The polymers exhibited good CO<sub>2</sub> uptake of 4.0 mmol g<sup>-1</sup> and moderate CO<sub>2</sub>/N<sub>2</sub> selectivities, thus exemplifying a simplistic approach to synthesizing highly functional polymers.<sup>35</sup> Kanatzidis, in 2011, reported a family of polymers synthesized using Bakelite-type chemistry with uniform, microporous, spherical particles and exhibiting surface areas up to 917 m<sup>2</sup> g<sup>-1</sup>.36 Internally, the micropores are adorned with many -OH reactive groups that can be functionalized. The POFs collect as much as 18% of their mass of CO<sub>2</sub> at atmospheric pressure. In 2015, our group reported a triazineresorcinol based POF with polar pore environment exhibiting very good CO<sub>2</sub> adsorption properties along with their water repelling nature, and high stability to SOx, NOx and steam

In this work, we have synthesized three isostructural polymers using the simplistic solvothermal reaction of pyrrole with trialdehyde-based monomers, which show the same pore size but different pore volumes. The effect of change in pore volume

on the  $\rm CO_2$  capacity is explored. And the potential of the POFs to separate  $\rm CO_2/N_2$  and  $\rm CO_2/CH_4$  has been studied. These polymers also exhibit moderate heat of adsorption and hydrophobicity, which is crucial for capturing  $\rm CO_2$  from the humid flue gas stream without compromising the  $\rm CO_2$  capacity.

### Results and discussion

We report three isostructural microporous polymers (IISERP-POF15 (1), IISERP-POF16 (2), IISERP-POF17 (3), where IISERP stands for Indian Institute of Science Education and Research Pune, synthesized without metal catalysts. The synthesis is carried out solvothermally at 493 K in 1,4 dioxane for 48 hours (Fig. 1). Importantly, the polymer's backbone consists of C-C, which imparts exceptional thermal and chemical stability, and the catalyst-free synthesis facilitates the easy scale-up. They are characterized by solid-state magic angle spinning NMR spectroscopy; the NMR results clearly show the presence of carbon (C-OH) on the aldehyde monomer. As the number of carbons (C-OH) increases from 1 to 3, the increase in the intensity of this peak at 153 ppm is also observed (Fig. 2A). The peak corresponding to the alpha carbon of the pyrrole is also observed in the solid-state magic angle spinning NMR. However, the most interesting and characteristic peak for the polymer in the NMR appears at 65 ppm, corresponds to the aldehydic C of the monomer bound to the alpha carbon of pyrrole through the C-C bonds (Fig. 2A). IR spectroscopy confirms the presence of free OH groups in these polymers. The stretching vibration mode of the O-H bond at  $\sim 3500$  cm<sup>-1</sup> as well as the characteristic for hydrogen bonding, broad absorbance between 3400 and 2900 cm<sup>-1</sup>, is present in all the spectra confirming the formation

Fig. 1 Synthesis scheme of 1, 2, and 3.

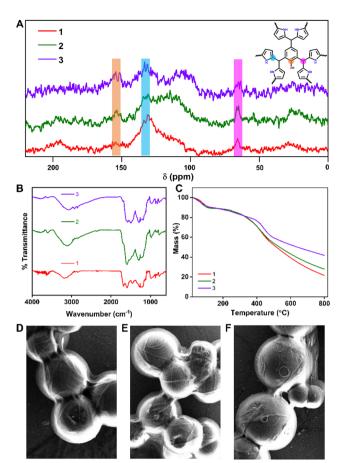


Fig. 2 (A) Solid state NMR of POFs showing the characteristic peaks. (B) IR-spectra of the POFs showing the peaks corresponding to the different stretching frequencies. (C) Thermo-gravimetric analysis of the POFs showing the high thermal stability. (D)-(F) FE-SEM morphology of 1, 2 and 3 respectively. (SEM images with the scale bar are shown in the ESI†).

of the polymers (Fig. 2B). These results are in agreement with the solid-state magic angle spinning NMR. The thermo-gravimetric analysis proves the excellent thermal stability (>350 °C/623 K) for all three polymers; around 20% of the total mass is lost up to 350 °C temperature, and this can be attributed to the solvents residing in the ultra micropores of the polymers (Fig. 2C). Powder X-ray diffraction does not show any sharp peaks confirming the amorphous nature of the POFs (Fig. S1, ESI†). The FE-SEM images show a very homogeneous and similar morphology for all three polymers; they consist of spherical balls inter-grown into clusters (Fig. 2D-F and Fig. S2-S4, ESI†). TEM images also showed similar morphology with uniform micropores on the surface (Fig. S5, ESI†).

The permanent porosity is established by 273 K CO<sub>2</sub> adsorption isotherms; all three POFs show a Type I isotherm. 1, 2 and 3 show  $CO_2$  uptakes of 3, 2.6 and 2 mmol  $g^{-1}$  at 273 K, respectively (Fig. 3A-C). The BET fit to the isotherms yields a BET area of 277, 235 and 213 m<sup>2</sup> g<sup>-1</sup> and a Langmuir surface area of 345, 289, and 260 m $^2$  g $^{-1}$  for 1, 2, and 3, respectively (Fig. S6-S11, ESI†). There is a consistent decrease in the CO<sub>2</sub> uptake capacity with the increase in the -OH groups in the polymers. The non-local density functional theory (NL-DFT) fit

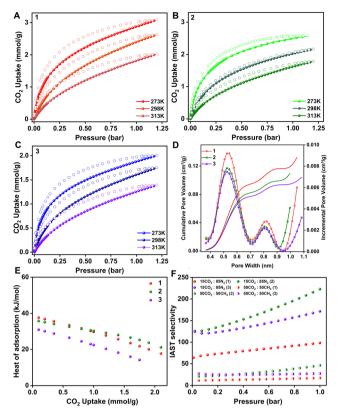


Fig. 3 (A) Equilibrium CO<sub>2</sub> adsorption isotherms on 1 at different temperatures. (B) Equilibrium CO2 adsorption isotherms on 2 at different temperatures. (C) Equilibrium CO<sub>2</sub> adsorption isotherms on 3 at different temperatures. (D) Pore size and pore volume distribution of POFs obtained by NLDFT fit to the 273 K CO2 isotherm. (E) Heat of adsorption plot for POFs calculated using the Virial method. (F) IAST selectivity of POFs for CO<sub>2</sub>/N<sub>2</sub> and CO<sub>2</sub>/CH<sub>4</sub> gas mixtures.

to the adsorption branch of the 273 K CO<sub>2</sub> isotherm yields a pore size of 0.55 nm in all three cases. However, the pore volume reduced with the increase in the number of hydroxyl groups in the framework (Fig. 3D). Since the POFs are isostructural with the same pore size, a direct correlation between the CO<sub>2</sub> uptake and the pore volume can be made. Hence to design better materials, it is not sufficient to have only ultramicropores, but maintaining the pore volume on the higher side of the scale is also crucial. Based on this observation, an ideal case would be to have a material with small apertures (<0.6 nm), which allows only the selective gas molecules to enter through the molecular sieving effect, with a cage-like cavity of larger volumes that can collect large amounts of gas resulting in high working capacity and selectivity. The CO2 isotherms were also performed at 298 K and 313 K for all the POFs. The CO<sub>2</sub> heat of adsorption was calculated by fitting the pure component isotherms to the virial model and nominal heat of adsorption values were obtained; 37.6, 35.7, and 31.9 kJ mol<sup>-1</sup> for 1, 2 and 3, respectively, at zero coverage. They decrease linearly with an increase in the loading of gas molecules, signifying the pore-filling mode of adsorption and the absence of any specific strong binding site or the cooperativity among the guest molecules (Fig. 3E and Fig. S12-S14 and

**Materials Advances** Paper

Table S1, ESI†). In order to estimate the ability of our POFs towards selective CO2 capture, we measured the pure component N2 and CH4 isotherms at ambient conditions and 0.11, 0.09 and 0.07 mmol  $g^{-1}$  of nitrogen and 0.55, 0.4 and  $0.28 \text{ mmol g}^{-1}$  of methane were adsorbed by 1, 2 and 3, respectively. The pure component adsorption isotherms were fitted using the Dual Site Langmuir (DSL) model, and IAST was employed to calculate the selectivity at different concentrations (Fig. S15-S23 and Table S2, ESI†). The CO<sub>2</sub>/N<sub>2</sub> IAST selectivity for the flue gas composition was estimated to be 98, 222, and 171 for 1, 2, and 3, respectively. In the case of CO<sub>2</sub>/CH<sub>4</sub>, the selectivity for a 50:50 composition is 17, 45, and 28 for 1, 2, and 3, respectively (Fig. 3F). These numbers are relatively lower compared to the CO<sub>2</sub>/N<sub>2</sub> selectivity because of high methane uptakes as compared to nitrogen. To determine the CO2 working capacity of the polymers under the mixed gas stream (15CO2:85N2), ideal adsorbed solution theory (IAST) was employed. The mixed gas isotherms were simulated using the IAST + + software, 38 which reveals that the saturation capacity of CO2 for a 15CO2:85N2 gas mixture is 0.87, 0.89 and  $0.65 \text{ mmol g}^{-1}$  for 1, 2 and 3, respectively (Fig. 4A).

Practical CO2 separation is carried out under dynamic conditions; the adsorbent should have facile diffusion within the polymer. To determine the adsorption kinetics, the CO<sub>2</sub> selfdiffusion coefficient was calculated as a function of CO2 loading and it comes out to be  $5 \times 10^{-9}$  m<sup>2</sup> s<sup>-1</sup> (Fig. 4B), which is much superior to the traditional sorbents such as zeolites. Stability is another key aspect that determines the quality of the adsorbent. The flue gas from which we aim to capture CO<sub>2</sub> consists of water vapors, and acidic gases such as SO<sub>x</sub> and NO<sub>x</sub> in addition to CO<sub>2</sub> and N<sub>2</sub>.<sup>39</sup> Since in the flue gas, CO<sub>2</sub> and N<sub>2</sub> are mixed with acidic gases, demonstrating the stability of adsorbents under such

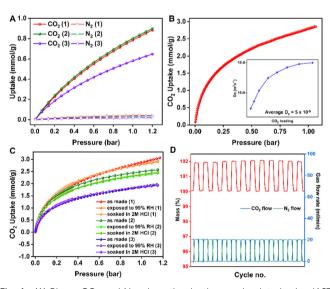


Fig. 4 (A) Binary CO<sub>2</sub> and N<sub>2</sub> adsorption isotherms simulated using IAST for 15CO2: 85N2. (B) High resolution 273 K adsorption isotherm of 1 used in this diffusion modelling. Inset shows the CO2 self-diffusion coefficients from kinetics measurement. (C) 273 K CO<sub>2</sub> adsorption isotherms performed on samples exposed to different conditions. (D) Gravimetric CO<sub>2</sub>-N<sub>2</sub> cycling performed on 1

harsh acidic conditions would be meaningful. This is a key property of all-organic C-C bonded porous polymers which could give them an edge over MOFs or other inorganic sorbents. To verify this, we carried out 273 K CO<sub>2</sub> adsorption on the POF samples, which were soaked in 2 M HCl for 24 hours. And no loss in the saturation CO<sub>2</sub> capacity at 273 K was observed (Fig. 4C). Additionally, the POF samples exposed to 99% RH at 50 °C for 6 hours did not show any fall in the CO<sub>2</sub> uptake compared to the pristine POFs (Fig. 4C), revealing their hydrolytic stability. The cycling stability of the best-performer, 1, was established by the TGA cycling experiment, which shows that the CO<sub>2</sub> working capacity does not fall even after 12 consecutive adsorptiondesorption cycles (Fig. 4D).

Water vapor in the flue gas can decompose the adsorbent if it is unstable in humid conditions. 40 Since water is a polar molecule, it can interact more strongly with the binding sites present in the adsorbent, and hence the positions which are supposed to be occupied by the CO<sub>2</sub> molecules can be taken up by the water molecules, resulting in the loss of working capacity. 41,42 To avoid this, the humid flue gas stream is pre-treated to adsorb water before it is fed to the CO<sub>2</sub>-capturing column, but this adds a parasitic load on the CCS process.<sup>43</sup> Hence if the adsorbent has water-repelling properties, it would be an additional advantage. 37,44 To decipher this, water sorption isotherms were carried out at two different temperatures for all the POFs, and a linear isotherm with a low uptake for 1 was observed. However, the uptake increased going from 1 to 3; also, the shape of the isotherm changed from nearlinear to Langmuir, depicting the stronger interaction of water molecules with the framework (Fig. 5A). Notably, 1, having the least number of OH functionalities, exhibits the most favorable CO<sub>2</sub> adsorption characteristics and has the least interaction with water. In order to check the surface hydrophobicity, we performed contact angle measurements. We observed that 1 is the most hydrophobic and 3 is the least, and 2 lies in between, all with a contact angle of > 90 (Fig. 5B-D). This confirms that 1

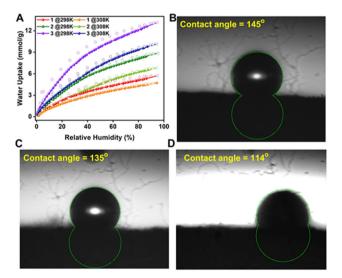


Fig. 5 (A) Water sorption isotherms for 1, 2, and 3. (B)-(D) Water contact angle of 1, 2, and 3.

**Materials Advances** Paper

has the most affinity for water, whereas 3 has the least. The plausible reason is that the number of framework OH groups capable of hydrogen bonding with the water increases from 1 to 3. Hence an increased affinity towards the water in 3 is observed. This could also mean that the hydrophobicity and hydrophilicity can be tuned in these POFs by fixing the number of waterattracting/repelling groups.

# Conclusions

In conclusion, we have synthesized three ultramicroporous POFs with similar pore sizes and different pore volumes in a catalyst-free manner. The difference in the pore volumes leads to various working capacities for CO<sub>2</sub>. They possess moderate HOA and good CO<sub>2</sub>/N<sub>2</sub> and CH<sub>4</sub> IAST selectivity. Water sorption isotherms and contact angle measurements on the three polymers revealed the hydrophilic/hydrophobic character of the materials, which is correlated with the number of phenolic -OH groups present in the material. The C-C bonded framework makes the polymers stable to harsh acidic conditions as well as under a high relative humidity of 99%, which is relevant to the humid flue gas capture. In the future, we aim to synthesize polymers with optimal pore sizes and the pore volume identified in this work, to access smooth adsorptiondesorption kinetics. Also, making a comparable polymer with no -OH functionality would give more insights into the role of the phenolic groups in providing CO<sub>2</sub> selectivity over water. Work is in progress.

# **Experimental**

#### Synthetic procedures

Synthesis of IISERP-POF15 (1). A solvothermal reaction between 2,4,6-triformylphenol (1 mmol) and pyrrole (2 mmol) in a solution containing 5 ml 1,4-dioxane was carried out at 493 K for 48 h. A black colored powder was isolated by filtration and was washed with THF. The air dried sample gave a yield of ~88%.

Synthesis of IISERP-POF16 (2). A solvothermal reaction between 2,4,6-triformylresorcinol (1 mmol) and pyrrole (2 mmol) in a solution containing 5 ml of 1,4-dioxane was carried out at 493 K for 48 h. A black colored powder was isolated by filtration and was washed with THF. The air dried sample gave a yield of  $\sim 88\%$ .

Synthesis of IISERP-POF17 (3). A solvothermal reaction between 2,4,6-triformylphloroglucinol (1 mmol) and pyrrole (2 mmol) in a solution containing 5 ml of 1,4-dioxane was carried out at 493 K for 48 h. A black colored powder was isolated by filtration and was washed with THF. The air dried sample gave a yield of  $\sim 88\%$ .

## Conflicts of interest

There are no conflicts to declare.

# Acknowledgements

We gratefully acknowledge IISER Pune for the financial support. H. D. S., P. S. thank CSIR for the funding. D. R. thanks IISER Pune for the funding. We gratefully acknowledge the Air Force Office of Scientific Research under award number FA2386-21-1-4022 for the funding and support. We acknowledge the SERB (CRG/2021/ 008250), the MHRD-FAST (MHRD Project 150 (F. No. 5-5/2014-TS-VII & F. No. 22-2/2016-TS-II/TC)) program, the MHRD-STARS[STARS1/278] program and the "DST-Nanomission under the Thematic Unit Program" (EMR/2016/003553).

### References

- 1 W. Wang, M. Zhou and D. Yuan, J. Mater. Chem. A, 2017, 5, 1334-1347.
- 2 https://climate.nasa.gov/vital-signs/carbon-dioxide/.
- 3 S. Chu, Science, 2009, 325, 1599.
- 4 K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T.-H. Bae and J. R. Long, Chem. Rev., 2012, 112, 724-781.
- 5 B. Li, Y. Zhang, R. Krishna, K. Yao, Y. Han, Z. Wu, D. Ma, Z. Shi, T. Pham, B. Space, J. Liu, P. K. Thallapally, J. Liu, M. Chrzanowski and S. Ma, J. Am. Chem. Soc., 2014, 136, 8654-8660.
- 6 A. Chowdhury, S. Bhattacharjee, R. Chatterjee and A. Bhaumik, J. CO2 Util., 2022, 65, 102236.
- 7 N. Das, R. Paul, D. Q. Dao, R. Chatterjee, K. Borah, S. Chandra Shit, A. Bhaumik and J. Mondal, ACS Appl. Nano Mater., 2022, 5, 5302-5315.
- 8 X. Zhu, S. M. Mahurin, S.-H. An, C.-L. Do-Thanh, C. Tian, Y. Li, L. W. Gill, E. W. Hagaman, Z. Bian, J.-H. Zhou, J. Hu, H. Liu and S. Dai, Chem. Commun., 2014, 50, 7933-7936.
- 9 Y. Luo, B. Li, W. Wang, K. Wu and B. Tan, Adv. Mater., 2012, 24, 5703-5707.
- 10 J. Lu and J. Zhang, J. Mater. Chem. A, 2014, 2, 13831-13834.
- 11 D. Yuan, W. Lu, D. Zhao and H. C. Zhou, Adv. Mater., 2011, 23, 3723-3725.
- 12 C. F. Martín, E. Stöckel, R. Clowes, D. J. Adams, A. I. Cooper, J. J. Pis, F. Rubiera and C. Pevida, J. Mater. Chem., 2011, 21, 5475-5483.
- 13 K. Huang, F. Liu and S. Dai, J. Mater. Chem. A, 2016, 4, 13063-13070.
- 14 X. Zhang, Y.-Z. Lv, X.-L. Liu, G.-J. Du, S.-H. Yan, J. Liu and Z. Zhao, RSC Adv., 2016, 6, 76957–76963.
- 15 A. K. Sekizkardes, P. Wang, J. Hoffman, S. Budhathoki and D. Hopkinson, Mater. Adv., 2022, 3, 6668-6686.
- 16 A. Roy, N. Haque, R. Chatterjee, S. Biswas, A. Bhaumik, M. Sarkar and S. M. Islam, New J. Chem., 2023, 47, 6673-6684.
- 17 S. N. Bhaduri, D. Ghosh, S. Chatterjee, R. Biswas, R. Banerjee, A. Bhaumik and P. Biswas, Inorg. Chem., 2022, 61, 18390–18399.
- 18 S. Dalapati, S. Jin, J. Gao, Y. Xu, A. Nagai and D. Jiang, J. Am. Chem. Soc., 2013, 135, 17310-17313.
- 19 B. Adhikari and S. Majumdar, Prog. Polym. Sci., 2004, 29, 699-766.

Paper

20 C. R. McNeill and N. C. Greenham, Adv. Mater., 2009, 21,

- 3840-3850. 21 V. Gautam, D. Rand, Y. Hanein and K. Narayan, Adv. Mater., 2014, 26, 1751-1756.
- 22 C. Yang, H. Wei, L. Guan, J. Guo, Y. Wang, X. Yan, X. Zhang, S. Wei and Z. Guo, *I. Mater. Chem. A*, 2015, 3, 14929–14941.
- 23 D. Rase, R. Illathvalappil, H. D. Singh, P. Shekhar, L. S. Leo, D. Chakraborty, S. Haldar, A. Shelke, T. G. Ajithkumar and R. Vaidhyanathan, Nanoscale Horiz., 2023, 8, 224-234.
- 24 M. Niu, H. Yang, X. Zhang, Y. Wang and A. Tang, ACS Appl. Mater. Interfaces, 2016, 8, 17312-17320.
- 25 C. Chen, W.-J. Son, K.-S. You, J.-W. Ahn and W.-S. Ahn, Chem. Eng. J., 2010, 161, 46-52.
- 26 J.-B. Lin, T. T. Nguyen, R. Vaidhyanathan, J. Burner, J. M. Taylor, H. Durekova, F. Akhtar, R. K. Mah, O. Ghaffari-Nik, S. Marx, N. Fylstra, S. S. Iremonger, K. W. Dawson, P. Sarkar, P. Hovington, A. Rajendran, T. K. Woo and G. K. H. Shimizu, Science, 2021, 374, 1464-1469.
- 27 H. A. Patel, J. Byun and C. T. Yavuz, ChemSusChem, 2017, 10, 1303-1317.
- 28 P. Arab, M. G. Rabbani, A. K. Sekizkardes, T. İslamoğlu and H. M. El-Kaderi, Chem. Mater., 2014, 26, 1385-1392.
- 29 K. S. Song, P. W. Fritz and A. Coskun, Chem. Soc. Rev., 2022, **51**, 9831-9852.
- 30 B. Lopez-Iglesias, F. Suárez-García, C. Aguilar-Lugo, A. González Ortega, C. Bartolomé, J. M. Martínez-Ilarduya, J. G. de la Campa, Á. E. Lozano and C. Álvarez, ACS Appl. Mater. Interfaces, 2018, 10, 26195-26205.

- 31 P. Kuhn, M. Antonietti and A. Thomas, Angew. Chem., Int. Ed., 2008, 47, 3450-3453.
- 32 P. Katekomol, J. R. M. Roeser, M. Bojdys, J. Weber and A. Thomas, Chem. Mater., 2013, 25, 1542-1548.
- 33 X. Zhu, C. Tian, G. M. Veith, C. W. Abney, J. R. M. Dehaudt and S. Dai, J. Am. Chem. Soc., 2016, 138, 11497-11500.
- 34 S. Zulfigar, M. I. Sarwar and C. T. Yavuz, RSC Adv., 2014, 4, 52263-52269.
- 35 J. Yan, B. Zhang, S. Guo and Z. Wang, ACS Appl. Nano Mater., 2021, 4, 10565-10574.
- 36 A. P. Katsoulidis and M. G. Kanatzidis, Chem. Mater., 2011, 23, 1818-1824.
- 37 S. Nandi, U. Werner-Zwanziger and R. Vaidhyanathan, J. Mater. Chem. A, 2015, 3, 21116-21122.
- 38 S. Lee, J. H. Lee and J. Kim, Korean J. Chem. Eng., 2018, 35, 214-221.
- 39 J.-Y. Lee, T. C. Keener and Y. J. Yang, J. Air Waste Manage. Assoc., 2009, 59, 725-732.
- 40 Y. Li and R. T. Yang, Langmuir, 2007, 23, 12937-12944.
- 41 L. Joos, J. A. Swisher and B. Smit, Langmuir, 2013, 29, 15936-15942.
- 42 J. G. Bell, M. J. Benham and K. M. Thomas, Energy Fuels, 2021, 35, 8102-8116.
- 43 H. A. Evans, D. Mullangi, Z. Deng, Y. Wang, S. B. Peh, F. Wei, J. Wang, C. M. Brown, D. Zhao, P. Canepa and A. K. Cheetham, Sci. Adv., 2022, 8, eade1473.
- 44 T. Wu, L. Shen, M. Luebbers, C. Hu, Q. Chen, Z. Ni and R. I. Masel, Chem. Commun., 2010, 46, 6120-6122.