Nanoscale Advances



REVIEW

View Article Online
View Journal | View Issue



Cite this: Nanoscale Adv., 2024, 6, 4781

Metal oxide-based photocatalysts for the efficient degradation of organic pollutants for a sustainable environment: a review

Abdullah Al Miad,^a Shassatha Paul Saikat,^a Md. Kawcher Alam,^{ab} Md. Sahadat Hossain, ^b Newaz Mohammed Bahadur^a and Samina Ahmed *b**

Photocatalytic degradation is a highly efficient technique for eliminating organic pollutants such as antibiotics, organic dyes, toluene, nitrobenzene, cyclohexane, and refinery oil from the environment. The effects of operating conditions, concentrations of contaminants and catalysts, and their impact on the rate of deterioration are the key focuses of this review. This method utilizes light-activated semiconductor catalysts to generate reactive oxygen species that break down contaminants. Modified photocatalysts, such as metal oxides, doped metal oxides, and composite materials, enhance the effectiveness of photocatalytic degradation by improving light absorption and charge separation. Furthermore, operational conditions such as pH, temperature, and light intensity also play a crucial role in enhancing the degradation process. The results indicated that both high pollutant and catalyst concentrations improve the degradation rate up to a threshold, beyond which no significant benefits are observed. The optimal operational conditions were found to significantly enhance photocatalytic efficiency, with a marked increase in degradation rates under ideal settings. Antibiotics and organic dyes generally follow intricate degradation pathways, resulting in the breakdown of these substances into smaller, less detrimental compounds. On the other hand, hydrocarbons such as toluene and cyclohexane, along with nitrobenzene, may necessitate many stages to achieve complete mineralization. Several factors that affect the efficiency of degradation are the characteristics of the photocatalyst, pollutant concentration, light intensity, and the existence of co-catalysts. This approach offers a sustainable alternative for minimizing the amount of organic pollutants present in the environment, contributing to cleaner air and water. Photocatalytic degradation hence holds tremendous potential for remediation of the environment

Received 23rd June 2024 Accepted 14th August 2024

DOI: 10.1039/d4na00517a

rsc.li/nanoscale-advances

Introduction

Urbanization and industrialization are cornerstones of modern civilization, underpinning significant advances in economic growth, technological innovation, and improved standards of living.¹ These processes have facilitated the development of cities, expanded infrastructure, and increased industrial productivity, creating myriad opportunities for societal progress.²,³ However, the rapid pace of urbanization and industrialization has also ushered in substantial environmental challenges, particularly through the generation of wastewater that contains a diverse array of organic pollutants.⁴-6 These pollutants are frequently hazardous, presenting significant hazards to both the environment and public health, in contrast

to conventional treatment procedures. 7-9 Industrial operations are major contributors to wastewater pollution, as they produce effluents laden with complex organic chemicals.10-12 These chemicals are often by-products of various industrial processes and include a wide variety of substances such as antibiotics, organic dyes, nitrobenzene, cyclohexane, phenols, toluene, biphenyls, pesticides, fertilizers, hydrocarbons, plasticizing greases, agents, detergents, oils, proteins, carbohydrates. 13-15 The environmental impact of these pollutants is profound, as they can persist in the environment, bioaccumulate in wildlife, and enter human food chains, leading to chronic health issues and ecological damage. 16,17 The complexity and resilience of these organic pollutants necessitate the development of advanced treatment technologies. 18,19 Traditional biological treatment methods are often inadequate for fully degrading these pollutants due to their toxicity and chemical stability. In response to this challenge, Advanced Oxidation Processes (AOPs) have been developed and are increasingly being employed for the effective degradation of hazardous organic contaminants present in wastewater.20-22

^aDepartment of Applied Chemistry and Chemical Engineering, Noakhali Science and Technology University, Noakhali, Bangladesh

bInstitute of Glass and Ceramic Research and Testing (IGCRT), Bangladesh Council of Scientific and Industrial Research (BCSIR), Dr Qudrat-i-Khuda Road, Dhanmondi, Dhaka-1205, Bangladesh. E-mail: shanta_samina@yahoo.com

Nanoscale Advances Review

AOPs are distinguished by the production of extremely reactive species, such as hydroxyl radicals, that can indiscriminately oxidize a broad spectrum of organic pollutants. This process converts the pollutants into less dangerous chemicals or fully mineralizes them into carbon dioxide (CO₂) and water (H₂O).²³ Among the various AOPs, photocatalytic degradation stands out as a particularly effective method.20 Photocatalysis involves the use of semiconductor materials as catalysts to accelerate chemical reactions upon exposure to light. When semiconductor materials such as zinc oxide (ZnO), iron oxide (Fe₂O₃), titanium dioxide (TiO₂), gallium phosphide (GaP), cadmium sulfide (CdS), and zinc sulfide (ZnS) are exposed to light, they generate electron-hole pairs that can generate reactive oxygen species.24-26 These reactive species possess the very capability of breaking down complex organic pollutants into less harmful, simpler molecules and fully mineralizing them.27,28 The advantages of photocatalysis are numerous and include low operational costs, the ability to accomplish full mineralization of contaminants without generating secondary pollution, and the capability to operate at ambient temperatures and pressures.29 Among the various photocatalysts, titanium dioxide (TiO₂) is the most extensively studied and broadly applied because of its exceptional chemical and photochemical stability, cost-effectiveness, low toxicity, and high activity under ultraviolet (UV) light. TiO2, with its wide band gap of approximately 3.2 eV, can mineralize a broad spectrum of organic contaminants, including herbicides, dyes, pesticides, phenolic compounds, and pharmaceuticals like tetracycline and sulfamethazine.30,31 Nevertheless, the actual utilization of TiO2 is somewhat restricted due to its dependence on UV light, which comprises just a minor portion of the solar spectral region.³² To overcome this limitation, other semiconductor materials with broader light absorption properties are being explored. Tungsten trioxide (WO3) has emerged as a promising alternative due to its capability of absorbing visible light, making it more competent for photocatalytic oxidation of volatile organic pollutants under natural sunlight.33,34 Additionally, silver nanoparticles (AgNPs) have gained significant attention as photocatalysts due to their high photostability, environmental friendliness, and catalytic properties that are dependent on their shape and size.35 The effectiveness of photocatalytic systems in degrading organic pollutants is dependent on numerous operational parameters. These factors encompass the substrate concentration, photocatalyst quantity, pH of the solution, reaction medium temperature, light irradiation duration and intensity, photocatalyst surface area, dissolved oxygen content in the reaction medium, and the characteristics of both the photocatalyst and substrate. 29,36,37 Furthermore, the doping of photocatalysts with metal and non-metal ions can enhance their photocatalytic activity by modifying their electronic properties and extending their light absorption range.³⁸ It is important to optimize these parameters to maximize the degradation kinetics and overall efficiency of photocatalytic processes.39 For instance, the proportion of the substrate to the photocatalyst must be carefully balanced to ensure that there are enough reactive sites for pollutant molecules to adsorb and react.37 The pH of the solution can affect the charge and surface

properties of the photocatalyst, influencing its interaction with pollutants. Temperature and light intensity also play significant roles in determining the rate of photocatalytic reactions, with higher temperatures and light intensities generally leading to increased reaction rates.40-42 In this review, we focused on the degradation of six specific types of organic pollutants: antibiotics, organic dyes, nitrobenzene, toluene, oil, and cyclohexane. These pollutants represent a broad spectrum of chemical structures and environmental impacts, making them ideal candidates for studying the effectiveness of various photocatalysts under different operational conditions. We will delve into the various reaction parameters that are critical to achieving maximum degradation of these pollutants using different photocatalysts. This comprehensive analysis aims to provide insights into the optimal conditions and catalyst selections for effective wastewater treatment, contributing to the mitigation of environmental pollution and the protection of aquatic ecosystems.

Photocatalytic degradation of chemical pollutants (organic dyes and antibiotics)

Chemical pollutants refer to a large group of contaminants that arise from different sources, including pharmaceuticals,43 personal care items,44 pesticides,45 and other synthetic chemicals.46 Chemical pollutants, such as antibiotics and organic dyes, have significant adverse effects on the environment.47 Antibiotics, encompassing classes such as beta-lactams (e.g., penicillins, cephalosporins), macrolides (e.g., erythromycin), tetracyclines (e.g., doxycycline), aminoglycosides (e.g., gentamicin), quinolones (e.g., ciprofloxacin), sulfonamides (e.g., sulfamethoxazole), glycopeptides (e.g., vancomycin), and oxazolidinones (e.g., linezolid), are significant pharmaceutical pollutants. 48 Organic dyes, including azo dyes (e.g., methyl orange), anthraquinone dyes (e.g., alizarin), phthalocyanine dyes (e.g., copper phthalocyanine), triphenylmethane dyes (e.g., malachite green), xanthene dyes (e.g., fluorescein), and indigoid dyes (e.g., indigo carmine), are prevalent industrial pollutants. 49 Both types of pollutants are persistent in water bodies, posing substantial dangers to aquatic ecosystems and human health due to their toxicity, bioaccumulation potential, and the propagation of antibiotic-resistant bacteria. 50,51 The persistence and toxicity of these chemical pollutants necessitate effective remediation strategies, such as photocatalytic degradation, which utilizes light-activated catalysts to break down these harmful substances into harmless by-products, ensuring cleaner water and healthier ecosystems.52

Organic dyes

A significant group of synthetic organic molecules produced by a variety of industries, including the leather, plastic, food, paper, textile, and medicinal sectors, are known as dyes.^{35,53} Due to their frequent application in various manufacturing sectors, dyes are inevitably accidentally released into the environment,

Review Nanoscale Advances

particularly into either surface water or groundwater, where they may pose serious dangers to environmental and biological systems.54-57 Over 700 000 tons of dyes are generated globally each year; 20% of these lost dyes reach the atmosphere and create pollution throughout processing or manufacturing, accounting for about 12% of the global total of dye generation. So the degradation of these organic dyes is necessary for maintaining the ecological balance.58 Organic dyes are very detrimental to aquatic ecosystems, even at low concentrations (less than 1 ppm). Thus, it is essential and required to remove organic dyes from effluents.59 The degradation mechanism of methylene blue dye is as follows.60

Photocatalyst + $h\nu$ (photon) \rightarrow Photocatalyst ($e_{cb}^- + h_{vb}^+$) (1)

$$e_{cb}^- + O_2 \rightarrow {}^{\bullet}O_2^- \tag{2}$$

$$h_{vb}^{+} + H_2O \rightarrow \cdot OH + H^{+}$$
 (3)

$$h_{vh}^{+} + OH^{-} \rightarrow OH$$
 (4)

Methylene blue + 'OH
$$\rightarrow$$
 Degradation products (5)

Methylene blue +
$${}^{\cdot}O_2^- \rightarrow Degradation products$$
 (6)

Degradation products + ${}^{\bullet}OH/O_2 \rightarrow$

$$CO_2 + H_2O + Inorganic ions$$
 (7)

Several metal oxides, such as ZnO, MgO, AgO, TiO₂, Fe₂O₃, Mn₂O₃, CuO, and V₂O₅, are frequently employed as photocatalysts in wastewater treatment processes to degrade dyes.61 Zinc oxide (ZnO) is an oxidizing substance found in nature as the unusual mineral zincite. There have been attempts to use ZnO alongside other semiconductors for the photocatalytic degradation of an extensive variety of biological pollutants.62 ZnO-based photocatalysts work according to various parameter conditions. These parameters are mainly Ph, the initial concentration of dye or catalyst, the wavelength of the light & so on. The photocatalytic reaction rate at the outermost layer of the catalyst can be influenced by the initial concentration of the substrate. To prevent the dispersion of light and the concentration impact of the exposed photocatalyst surface, the ideal photocatalyst concentration ought to be unique for heterogeneous photocatalysis processes. 63 Velmurugan et al. stated that the rate of degradation k dropped from 0.173 to 0.012 min^{-1} when the dye concentration was increased from 1 \times 10⁻⁴ to 4 \times 10⁻⁴ M.⁶⁴ This is because many layers of adsorbed dye molecules have formed on the outermost layer of the catalyst, which prevents the photoreaction from occurring because there was not enough direct light interaction to produce hydroxyl radicals.65 The first amount of dye has a significant influence on the degradation efficiency of MB.66 Sobana et al. used ZnO that was manually combined with activated carbon (AC-ZnO) and solar irradiation to study the impact of initial Direct Blue 53 (DB53) concentration over the concentration range from 1×10^{-4} to 9 × 10⁻⁴ M.⁶⁷ Its numerous functions make it extremely difficult to determine how the pH of a solution affects the efficacy of the dye photocatalytic degradation activity.68 Velmurugan et al.

stated the impact of pH in the range of 3-11 upon the photocatalytic breakdown of Reactive Red 120 (RR 120) over ZnO during solar light irradiation.64 Photocatalytic breakdown of Reactive Orange 4 (RO4) and Black 5 (RB5) dyes occurs at various solution pH levels between 3 and 11.69 The pH, which regulates the adsorption of organic compounds on the outermost layer of the photocatalyst, serves as one of the most crucial factors influencing photocatalysis effectiveness.70 Electromagnetic relationships between the outermost layer of the photocatalyst and the substrate of interest can be employed to clarify how pH affects photocatalysis outcomes.27 Singh et al. stated that after exposing ZnO nanorods to UV radiation for 120 minutes, photodegradation activity levels were 7.169% and 47.63% for pH values of 4.5 and 10.5, correspondingly.⁷¹

Scientists' interest has been drawn more and more to supported TiO₂ catalyst utilization over the past few years due to its prospective uses in the photocatalytic breakdown of organic contaminants such as organic dyes in air and water. Additionally, reports have it that when adsorbents are used to support TiO2, an ideal condition is created for the elimination or degradation of the compounds of interest. 72,73 To enhance TiO2based photocatalysts on organic dye in wastewater, several conditions were adjusted. These crucial elements, which included light intensity, TiO2 form and structure, target type, pH level and doping type, all had an impact on the photocatalysis method's effectiveness.58 If we want to discuss the parameters it is found that it is rather tough to comprehend how pH impacts the photodegradation process's efficacy.²⁹ TiO₂ exhibits amphoteric properties, allowing for the development of either a positive or negative charge on its outermost layer.74 Due to this, the adsorption of dye molecules over TiO2 surfaces may be affected by changes in pH.75 Bubacz et al. found that when pH is increased, so did the rate at which methylene blue was broken down photo-catalytically.76 On the other hand, Neppolian et al. showed that acidic conditions do not affect the degradation rate of the Reactive Blue 4 significantly enough.77 It has been found that organic dyes like Reactive Black 5 and Reactive Orange 4 degradation were enhanced in an acidic solution containing TiO2.69 Tanaka et al. discovered that at less acidic values, the positively charged TiO2 layer absorbed more Acid Orange 7, and greater breakdown was accomplished.78 A study has been conducted on the effects of pH on the adsorption as well as decolorization of Procion Red MX-5B (MX-5B) and Cationic Blue X-GRL (CBX). It was discovered that when the pH increased, MX-5B's adsorption was reduced. 62 Another key parameter for dye degradation using a TiO₂ catalyst is the dye amount or dye concentration. It has been found that the increased initial concentration of the dyes increases the degradation rate.36,79 This is because when the dye's initial concentrations rise, the dye molecules become deposited on the outermost layer of the catalyst and consume a sizable proportion of UV light instead of the TiO2 nanoparticles.80,81 Neppolian et al. investigated how the original dye concentration affected the percentage of degradation. With the best possible catalyst loading, they changed the starting concentrations of Reactive Yellow 17 (from 8.9×10^{-4} to 1.29×10^{-3} M), Reactive Red 2 (from 4.169×10^{-4} to 1.259×10^{-3} M), and Reactive Blue 4

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Table 1 Data for the photocatalytic degradation of organic dyes using various catalysts a

Ref. 102 103 89 104 105 106 99 101 107 88 89 89 90 91 92 93 67 94 95 96 79 97 Degradation percentage 87% after 20 min, 70% 91% under visible light irradiation in 20 min, after 20 min, nearly 100% after 120 min 100% under UV %), time (min) 97.64%, 120 96.58%, 100 93.8%, 190 90.7%, 190 99.46%, 50 99.86%, 35 83,8%, 120 100%, 180 100%, 180 in 60 min 96%, 120 80%, 300 97%, 120 73%, 180 95%, 120 99.7%, 8 50%, 10 85%, 60 50%, 30 99%, 30 90%, 60 95%, 60 **—**, 720 -, 180High pressure Hg lamp, 300 High pressure Hg lamp, 50 High pressure Hg lamp, 150 Compact xenon lamp, 300 Mercury vapor lamp, 8 Metal halide lamp, 70 Tungsten lamp, 500 Tungsten lamp, 500 Tungsten lamp, 200 Halogen lamp, 100 Lamp, power (W) Xe arc lamp, 300 Xenon lamp, UV lamp, 40 40 40 UV light, pH = around 7 Solar light, degradation Operational conditions UV light (315–400 nm), pH = 2, temp = 80 $^{\circ}$ C pH = 2, temp = $80 \, ^{\circ}C$ UV light (315–40 nm), steadily increased up UV light, pH = 7.18, Solar light, pH = 6 UV light, pH = 7.0, Visible light; light Visible light; light intensity: 18.6 lux intensity: 18.6 lux Solar light, temp: UV light, pH = 2, = 4 $temp = 400 \, ^{\circ}C$ UV light, pH Visible light, Visible light Visible light Visible light temp: 80 °C emp: 25 °C Visible light UV, pH = 3UV light, to pH = 12UV/visible, UV light, UV light UV light pH = 7350 °C 0.0001 - 0.0005Catalyst conc. 0.0006-0.004 $(\text{mg }\check{\text{L}}^{-1})$ 0.00016 0.00050.004 500 400 Natural zeolite supported MgAl₂O₄ nanoparticles Cu-doped ZnO (NPs) Nanostructured TiO₂ CA-CNT/TiO₂-NH₂ CA-CNT/TiO₂-NH₂ 2% Al-2% Ni-ZnO Zn(L)(H2O)]·H2O Floral-like LaFeO₃ Mn-doped ZnO ZnO nanowires Undoped ZnO TiO2-NH2 NPs WO₃/Ag₂CO₃ $\text{TiO}_2/\text{g-C}_3\text{N}_4$ ZnO/Cn₂O Nano ZnO PbBiO,Br ZnO NFs Catalyst Ce-ZnO ZnO NPs Pollutant conc. $[\text{mg L}^{-1}]$ 20-60 63.97 0.001 23.4 100 50 10 10 30 30 75 50 10 64 10 -- 25 --15 10 10 2 Pollutants RO16 AR27 AR57 **AB25** RhB RhB RhB MB MB MB MO M M O M MB RhB MB TO MB \overline{C}

^a MB = Methylene Blue, IC = Indigo Carmine, RhB = Rhodamine B, AR57 = Acid Red 57, CR = Congo Red, MO = Methyl Orange, AR27 = Acid Red 27, AB25 = Acid Blue 25, RO16 = Reactive Orange 16.

Review Nanoscale Advances

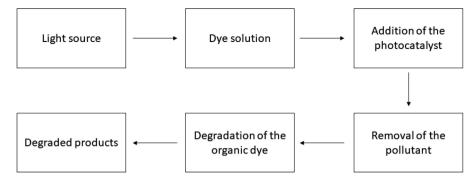


Fig. 1 Working procedure of the photocatalyst for dye degradation.

(from 1.9 \times 10⁻⁴ to 5.9 \times 10⁻⁴ M).⁷⁷ The dye degradation in a water-based solution utilizing a catalyst powder of TiO2 within a photocatalytic reactor is influenced by two additional parameters: the wavelength and intensity of the UV light irradiation source.82 Lower radiation wavelengths are thought to encourage the creation of electron holes, which would increase the catalyst's effectiveness.83 Ollis et al. said that at minimal light levels (0-20 mW cm⁻²), the rate would rise in an orderly manner as the intensity of light increased. The rate would rely on the square root of the light intensity at moderate light intensities (about 25 mW cm⁻²) but at intense light levels, the rate is independent of the light intensity.29,84 The degradation of Orange G was shown to be affected by light intensity in a range of 215 to 586 W cm⁻². With a rise in light magnitude, Orange G's photolysis reaction rates climbed.85 Rao et al. stated that Acid Orange 7 (AO7) photocatalytically breaks down at a pace that is roughly 1.5 times faster in direct sunlight compared to that under synthetic UV radiation.86 Another significant operational parameter for the organic dye degradation is temperature range.36 The range of 40-50 °C was determined to be the ideal operating temperature range. Since desorption of the produced products happens more slowly at low temperatures than interface degradation as well as reactant adsorption, it restricts the reaction. Conversely, the limiting step becomes the dve's adsorption on TiO2 at an elevated temperature.87 A table has been added showing the photocatalytic degradation of organic pollutants (Table 1) and the process is illustrated in Fig. 1. The rate constant is lowered at elevated temperatures due to the organics' and hydrated oxygen's reduced adsorptive ability. Consequently, the ideal temperature often falls between 293 and 353 K.108,109

Antibiotics

Due to their extremely stable and non-biodegradable nature, antibiotics accumulate in the ecosystem as a result of overuse and uncontrolled environmental discharge.110,111 The release of diverse antimicrobial pollutants and their varied toxicity provide a significant challenge for researchers trying to find a solution. 112,113 The excessive accumulation of antibiotics in natural environments has presented a significant peril to ecological systems. 114,115 Unfortunately, traditional water

treatment methods such as adsorption, filtration, and biodegradation are ineffective in effectively removing antibiotics due to their significant durability and limited biodegradability. Hence, the development of novel technologies is vital to ensure the efficient elimination of antibiotics.116-119 Due to its advantageous characteristics of cost-effectiveness, environmental sustainability, and high efficacy, heterogeneous photocatalysis has become a process of great promise for wastewater treatment, which relies on the direct utilization of sunlight to effectively degrade and subsequently mineralize organic pollutants, and has emerged as a promising approach to tackle diverse environmental challenges. 120-122 Furthermore, it is crucial to provide an overview of frequently utilized photocatalytic nanomaterials and their specific use in breaking down popular antibiotics. This is necessary to validate their practical superiority and efficacy as catalysts for the process of photodegradation. 123-125 The degradation mechanism of ciprofloxacin antibiotic in the presence of different photocatalysts is provided.126

Photocatalyst + $h\nu$ (photon) \rightarrow Photocatalyst ($e_{cb}^- + h_{vb}^+$) (8)

$$e_{cb}^{-} + O_2 \rightarrow {}^{\cdot}O_2^{-}$$
 (9)

$$h_{vb}^{+} + H_2O \rightarrow {}^{\bullet}OH + H^{+}$$
 (10)

$$h_{vb}^{+} + OH^{-} \rightarrow OH$$
 (11)

Ciprofloxacin +
$$OH \rightarrow Degradation products$$
 (12)

Ciprofloxacin +
$${}^{\cdot}O_2^- \rightarrow Degradation products$$
 (13)

Degradation products +
$${}^{\bullet}OH/O_2 \rightarrow$$

 $CO_2 + H_2O + Inorganic ions$ (14)

Yang et al. researched the degradation of ciprofloxacin using g-C₃N₄/TiO₂ nanocomposites with the help of visible light irradiation utilizing a 300 W Xe visible lamp where the authors observed 88% of CIP degraded in 180 minutes.127 Verma explored the degradation of amoxicillin (AMX) by the utilization of TiO2 photocatalysis and sono-photocatalysis and achieved the highest degradation rate (80%) of AMX at a pH of 7.0 under UV irradiation at a power density of 672 W m⁻². 128 Zhang examined the mechanism and kinetics of photocatalytic

Data for the photocatalytic degradation of antibiotics using various catalysts Table 2

Antibiotics a	Antibiotics conc. (mg L^{-1})	Catalysts	Catalyst conc. $({ m mg~L}^{-1})$	Operational conditions	Lamp, power (W)	Degradation percentage (%), time (min)	Ref.
CIP	10	$ m g\text{-}C_3N_4/TiO_2$	375	Visible light	Xe, 300	88, 180	127
AMX	30	TiO2	450	UV light, pH 7	672	80, 270	128
TC	50	3D-PDI	25	Visible light, pH 5	I	80, 150	129
APAP	0.7	BiTNMs	1000	Visible light, pH 7	200	88, 180	130
CFX	50	$ m NiS-PPY-Fe_3O_4$	4000	UV light, pH 5.5	Hg, 75	80, 30	131
SMZ	30	Cu-TiO ₂ @functionalized SWCNT	006	UV-vis light, pH 7	· 1	100, 300	132
CFT	15	$\mathrm{BN/CdAl}_2\mathrm{O}_4$	330	UV light, pH 7	108	100, 240	133
OFL	5	PVP capped BiOBr	10	Visible light	15	94, 240	134
NOR	5	PVP capped BiOBr	10	Visible light, pH 7.54	15	99.8, 240	134
TC-H	20	$\mathrm{CdTe/TiO}_2$	009	Visible light	300	78, 30	135
TC	0.01	$\mathrm{BiVO_4/TiO_2/RGO}$	I	Visible light, pH 3	Xe, 1000	96.2, 120	136
CTC	0.01	$\mathrm{BiVO_4/TiO_2/RGO}$	I	Visible light, pH 3	Xe, 1000	97.5, 120	136
OTC	0.01	$\mathrm{BiVO_4/TiO_2/RGO}$	I	Visible light, pH 3	Xe, 1000	98.7, 120	136
DXC	0.01	$\mathrm{BiVO_4/TiO_2/RGO}$	I	Visible light, pH 3	Xe, 1000	99.6, 120	136
CFX	20	$\mathrm{MnWO_4/Bi_2S_3}$	1200	Visible light	Xe, 1000	78.8, 180	137
MTZ	20	$\mathrm{MnWO_4/Bi_2S_3}$	1200	Visible light	Xe, 150	83.3, 180	137
TC	10	$\mathrm{SnO_2/CeO_2}$	200	Visible light, pH 9–10	200	97, 120	138
PG	5	ZnO	800	UV light, pH 6.8	24	72.72, 150	139
CIP	20	40TiHAp	2000	UV light, pH 6.1	125	100, 15	140
OFL	20	40TiHAp	2000	UV light, pH 6.1	125	100, 120	140
TC	10	$\mathrm{Cu_3P/ZnSnO_3/g-C_3N_4}$	500	Visible light	Xe, 500	98.45, 60	141
CEF	100	ACT-4	844	Visible light	LED bulb, 50	99.6, 260	142
OFL	10	$\mathrm{ZnO/Bi}_{2}\mathrm{MoO}_{6}$	250	Visible light, pH 7.54	Daylight lamp, 15	100, 240	143
TC	10	$\mathrm{MoO_3/g\text{-}C_3N_4}$	200	Visible light	I	85, 9100	144
TC, CPX, and/or	09	$\mathrm{Bi_2MoO_6}(\mathrm{@Bi_2MoO_{6-x}})$	300	Visible light, pH 7	LEDs, 6.2	>95, 180	145
LFC solution							
GMF	15-35	Zn-Co-LDH@BC	750	UV light, pH 5.5	10	92.7, 130	146
CFS	200	WO_3/g - C_3N_4	25	UV light	Xe, 300	82, 120	147
Lomefloxacin	10	$ m MgTiO_3$	30	UV light, pH 7	LED light, 30	83, 150	148
TC-HCl	20	$\mathrm{Bi_4Ti_3O_{12}}$	10	UV light	Xe, 300	75.5, 150	149
Cefazolin	20	${ m TiO}_2$	400	UV light, pH 5	15	96.47, 60	150
SMX	I	${ m TiO}_2$	0.002	UV light	Xenon, 1500	88, 360	151
SMX	10	${ m TiO}_2$	250	UV light, pH 4.1–5.4	0V, 9	Close to 100, 120	152
OA	20	Titanium Degussa P-25	0.001	pH 7.5	Black light lamp	90, 30	153
Norfloxacin	I	$C-TiO_2$	0.0002	Visible light	I	78, 70	154
TC	40	Metal ion@TiO $_2$ /HNTs		Visible light	Xenon, 500	76.54, —	155
Chloramphenicol	50	TiO_2	0.001	UV light	Osram Dulux, 9	90, 90	156
SMX	100	TiO_2	0.0005	UV light	Xenon lamp	80, 360	157

" CIP = ciprofloxacin, AMX = amoxicillin, TC = tetracycline, APAP = acetaminophen, CFX = cephalexin, SMZ = sulfamethoxazole, CFT = cefoxitin sodium, OFL = ofloxacin, NOR = norfloxacin, CTC = chlorotetracycline, OTC = oxytetracycline, MTZ = metronidazole, PG = penicillin G, CEF = cefixime, GMF = gemifloxacin, CFS = ceftazidime, SMX = sulfamethoxazole, OA = oxolinic acid.

Light source

Wastewater

Addition of the photocatalyst

Degraded products

Removal of the pollutant

Degradation of antibiotics by creating electron &

Fig. 2 Working procedure of the photocatalysts for antibiotic degradation.

degradation of tetracycline (TC) utilizing a supramolecular organic photocatalyst called three-dimensional network structure perylene diimide (3D-PDI).129 Fan et al. synthesized three different structures of bi-modified titanate nanomaterials (Bi-TNM) utilizing the hydrothermal technique and carefully adjusted variables to break down paracetamol (ACT). The study revealed that bi-titanate nanoribbons, when used at a concentration of 1 g L⁻¹, had the most effective photocatalytic degradation capability, achieving a rate of 88%. 130 The catalytic efficiency of NiS and NiS immobilized within the magnetite polypyrrole core/shell matrix (Fe₃O₄@PPY) was examined for the degradation of cephalexin. The study also examined the photocatalytic breakdown of cefalexin using the NiS-PPY-Fe₃O₄ photocatalyst, which was exposed to sunshine. The photocatalyst demonstrated a removal efficiency of over 80% over a 30 minute timeframe. 131 Payan studied the creation of photocatalysts using Cu-TiO2@functionalized single-walled carbon nanotubes and found that sulfamethazine can be fully destroyed under solar irradiation within 300 minutes. 132 R. Kumar et al. synthesized BN/CdAl₂O₄ composites and evaluated their photocatalytic ability to degrade cefoxitin sodium (CFT) antibiotic in an aqueous solution. The findings demonstrated that a nearly complete degradation of CFT, reaching approximately 100%, occurred within 240 minutes at a concentration of 15 mg L⁻¹ and a pH of 7.133 A bismuth oxybromide (BiOBr) photocatalyst capped with PVP was produced by a solvothermal technique. The PVP-capped BiOBr exhibits a removal efficiency of 94% and 99.8% for the antibiotics ofloxacin (OFL) and norfloxacin (NOR) respectively, when exposed to visible light.¹³⁴ Y. Gong prepared Z-scheme CdTe/ TiO₂ heterostructure photocatalysts decomposing 78% tetracycline hydrochloride (TC-H) within 30 min of irradiation under visible light.135 W. Wang examined the photocatalytic efficiency of BiVO₄/TiO₂/RGO composites for four tetracycline antibiotics. The BiVO₄/TiO₂/RGO photocatalyst demonstrated significant photocatalytic activity and compatibility, providing efficient separation of photo-generated carriers with oxidation capabilities and high reduction.136 N. Askari synthesized a novel heterojunction Z-scheme MnWO₄/Bi₂S₃ using a hydrothermal technique to study the photocatalytic behavior of catalysts in the decomposition of metronidazole (MTZ) and cephalexin (CFX) under LED light exposure where a maximum

degradation efficiency of 78.8% was achieved for CFX and 83.3% for MTZ.137 A. Mohammad et al. studied manufactured nanostructured photocatalysts composed of tin oxide (SnO2) and cerium oxide (CeO₂). These photocatalysts were employed to degrade the antibiotic tetracycline hydrochloride (TC) under visible light. The most optimal outcome seen among the examined photocatalysts had a TC removal effectiveness of approximately 97% within a 120 minute timeframe under visible-light exposure. 138 An investigation was conducted on the photocatalytic degradation of pharmaceutical micropollutants of Penicillin G (PG) in a photoreactor. The proficiency of the photocatalytic process was increased by the inclusion of persulfate sodium (PPS). The inclusion of PPS greatly enhanced the efficiency of the photolysis process, resulting in a considerable improvement of 72.72% compared to the traditional photocatalysis system, which achieved 56.71% efficiency. 139 Bouyarmane synthesized TiO₂-hydroxyapatite nanocomposites precipitating a re-dissolved natural phosphate mineral in ammonia using the concurrent gelation of titanium alkoxide. These nanocomposites were then subjected to degradation for drug testing in a solution under ultraviolet light. When utilizing 40TiHAp as a photocatalyst, ciprofloxacin and ofloxacin were destroyed through photodegradation in 15 minutes and 120 minutes, respectively.140 A simple solvothermal technique was employed to synthesize a novel Cu₃P-ZSO-CN p-n-n heterojunction photocatalyst for the degradation of the antibiotic tetracycline (TC) under exposure to visible light. The degradation efficiency for TC was found to be 98.45%.141 M. Abdullah et al. synthesized ACT-X nanocomposites using activated carbon and TiO2 to enhance the inherent characteristics of TiO2, resulting in improved light absorption in the visible area. The ACT-4 photocatalyst has demonstrated the maximum level of photocatalytic degradation (99.6%) for the ceftriaxone (CEF) antibiotic.142 The very first 3D hierarchical ZnO/Bi₂MoO₆ heterojunctions were synthesized using an in situ solvothermal technique. These heterojunctions exhibited a remarkable efficiency of 100% in the photodegradation of the ofloxacin (OFL) antibiotic. This exceptional performance can be ascribed to their reduced electron-hole recombination rate and large surface area.143 A novel heterojunction photocatalyst (MoO₃/g-C₃N₄) was synthesized using a straightforward hydrothermal calcination technique. The catalytic efficiency of

holes

 Table 3
 Data for the photocatalytic degradation of toluene using various catalysts

		n				
Toluene conc. (ppm)	Catalyst	Catalyst conc. $({ m mg~L}^{-1})$	Operational conditions	Lamp, power (W)	Degradation percentage (%), time (min)	Ref.
09	$ m In_2S_3/g\text{-}C_3N_4$	50	Visible light, RH 50–60%	Xe	89.7, 180	184
2	1 wt% rGO/S _{0.05} N _{0.1} TiO ₂	200	Visible light, RH 60%	Fluorescent, 10	72, 480	185
1900	$ m Ir\ doped-TiO_2$	100	UV light, RH 70%	UV, 25	97, 8.5	186
50	PIL@TiO ₂ /m-GO	1000	UV, RH 40%	UV, 8	97, 24	187
1	${ m TiO_2/Bi/Bi_2MoO_6}$	2000	UV	Xe, 320	26.08, 120	188
843	TiO ₂ /ACF-Ac fabricated	151.2	UV, RH 40%	Xe, 300	70, 2400	189
	$\mathrm{by}\;\mathrm{Zn}(\mathrm{CH_3COO})_2$					
30	Cu_2O NWs	172.26	Visible, RH 74%	Xe, 300	99.9, 120	190
09	$SrTiO_3/rGO$	400	UV light, RH 50%	UV, 8	98.65	191
50	TiO ₂ /Bentonite	200	UV light	UV lamp	64, 120	192
50	InOOH	400	UV light	Xe, 300	75.8, 60	183
30	C -USTiO $_2$	100	Visible light, RH 50%	LED, 1	80, 180	193
30	CeO_2	1000	VUV light, RH 50%	VUV, 4	83.2, 144	194
300	WO_3/TiO_2	Ι	LED light	I	95.4, 30	195
23.6	THS amorphous- TiO_2	10	UV light	UV, 8	98.2, 240	196
50	TiO_2/ND	100	UV	Xe, 50	100, 120	197
750	$\mathrm{ZnAl_2O_4}$	I	UV	Black-light fluorescent lamp	90.25, 300	198
I	${ m TiO}_2$	I	UV, RH 35%	Germicidal lamp, 15	61.9, 180	199
160	${ m TiO}_2$	I	UV, RH 25–50%	Black lamp, 10	50–60, 5	200
400	TiO_2	I	UV	Iron halogenide lamp, 500	52, 360	201
1	TiO_2	I	UV	Mercury lamp, 300	90, 120	202

2D MoO₃/g-C₃N₄ Z-scheme heterojunction outperformed the original g-C₃N₄ and achieved an impressive 85.9% removal efficiency within 100 minutes when exposed to visible light. 144 E. Gómez et al. fabricated highly efficient photocatalysts by using electrochemical deposition and thermal treatment. These photocatalysts, called nanostructured homojunction Bi₂MoO₆@Bi₂MoO_{6-x}, were able to effectively degrade and mineralize solutions containing various antibiotics (such as tetracycline, ciprofloxacin, and levofloxacin). After 180 minutes of radiation exposure, the photocatalysts achieved exceptionally high mineralization values (>95%) and near-complete degradation.145 P. Gholami et al. examined the photocatalytic efficacy of Zn-Co-layered double hydroxide (LDH) nanostructures containing charcoal (BC) in the breakdown of gemifloxacin (GMF), a representative pharmaceutical contaminant. The results indicate that 92.7% of GMF underwent degradation through photocatalysis in the presence of the Zn-Co-LDH catalyst. The effectiveness of BC-incorporated Zn-Co-LDH as a photocatalyst was greatly influenced by the concentration of the solute and the amount of photocatalyst used. 146 Elegant Z-scheme composite hollow microspheres (CHMs) were made by sequentially controlling in situ hydrolysis and polymerization of WO₃/g-C₃N₄. WO₃/g-C₃N₄ CHMs are the most effective for photocatalytic degradation of CFS, with an 82% degradation efficiency after 2 hours of visible-light irradiation. 147 Y. Sneha et al. conducted research on the properties of photocatalyst magnesium titanate (MgTiO₃) in the presence of visible light, specifically focusing on its interaction with lomefloxacin. The study found that a concentration of 30 mg L⁻¹ of catalyst was the most effective in breaking down 10 mg L⁻¹ of lomefloxacin using 30 W LED irradiation for a duration of 150 minutes. 148 The interaction between various surface facets of a semiconductor with suitable ratios can lead to improved performance in the degradation of photocatalytic processes. J. Wang et al. studied a material composed of bismuth called Bi₄Ti₃O₁₂ and found that it showed improved degradation activity for tetracycline hydrochloride (TC-HCl)

this photocatalyst was assessed by measuring its ability to

degrade tetracycline. The findings demonstrated that the 0D-

and Fig. 2 shows the process. The findings indicate that the breakdown percentage of TiO₂ suspension at favorable pH conditions (pH 5) is 96.47% after 60 minutes of irradiation.¹⁵⁰

Other industrial pollutants (toluene, nitrobenzene, cyclohexane, and refinery oil)

Industrial chemical pollutants are a subgroup of chemical pollutants specifically connected with industrial operations.¹⁵⁸ They encompass a wide spectrum of chemicals used or produced in manufacturing, refining, and other industrial processes. 159 Industrial chemical pollutants, including toluene, cyclohexane, nitrobenzene, and refinery oil, pose significant environmental threats due to their widespread use and high toxicity. 160,161 Toluene, an industrial solvent, pollutes air, water, and soil, causing harm to aquatic organisms and long-term environmental damage.162 Cyclohexane, used in chemical production, contributes to air and water pollution, affecting aquatic life.163 Nitrobenzene, a dye and pharmaceutical precursor, contaminates soil and water, posing toxic and carcinogenic risks.164 Refinery oil, a byproduct of petroleum refining, causes extensive damage through spills and leaks, affecting marine and terrestrial ecosystems. 165 Photocatalytic degradation is crucial for mitigating these pollutants, as it offers an efficient, eco-friendly method to break down these toxic substances, preventing their persistence in the environment and safeguarding both ecosystems and human health.166

Toluene

As one of the pollutants that pose a risk to human health and the ecosystem, toluene has been classified as a priority pollutant; for this reason, emission management is required. ^{167,168} Owing to the serious issues that toluene causes, various methods for toluene abatement have been developed. ¹⁶⁹ The rapid growth in industrialization and urbanization has played a notable role in the emergence of severe environmental issues. ^{170,171} Toluene, a volatile organic molecule, can induce skin inflammation, respiratory ailments, chronic and acute intoxication, neurotoxicity, and reproductive toxicity. ^{172–176} Therefore, it is necessary to enhance the efficacy of eliminating indoor toluene vapors. Methods to counteract atmospheric

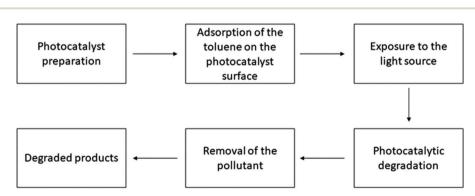


Fig. 3 Working procedure of the photocatalysts for toluene degradation.

when exposed to irradiation.¹⁴⁹ M. Shokri et al. investigated

the degradation of cefazolin through exposure to immobilized

and suspended TiO2 on a glass plate. A table has been added

showing the photocatalytic degradation of antibiotics Table 2

pollution can be classified as either chemical or physical approaches. ^{177,178} Physical approaches include adsorption, the process of condensation, and separating membranes. Chemical approaches encompass combustion, low-temperature plasma, biological, and photocatalytic treatments. ^{179,180} Photocatalysis is regarded as a very promising option for environmental cleaning among these techniques. Photocatalytic technologies provide the benefits of being non-toxic and cost-effective, requiring gentle reaction conditions, and producing no secondary pollutants. ^{136,181} Almost all the hydrocarbon degrades *via* the following mechanism. ^{182,183}

Nanoscale Advances

Photocatalyst + $h\nu$ (photon) \rightarrow Photocatalyst ($e_{cb}^- + h_{vb}^+$) (15)

$$e_{cb}^{-} + O_2 \rightarrow {}^{\cdot}O_2^{-}$$
 (16)

$$h_{vb}^{+} + H_2O \rightarrow OH + H^{+}$$
 (17)

$$h_{vb}^{+} + OH^{-} \rightarrow OH$$
 (18)

Toluene +
$$OH \rightarrow Hydroxylated intermediates$$
 (19)

Hydroxylated intermediates + 'OH → Degradation products(20)

Degradation products +
$${}^{\cdot}OH/O_2 \rightarrow$$

 $CO_2 + H_2O + Inorganic ions$ (21)

M. Zhang et al. utilized a hydrothermal technique to synthesize In₂S₃ in a nanoscale form. This nanomaterial was then employed to fabricate a composite photocatalyst consisting of In₂S₃ and g-C₃N₄. The process of toluene photocatalytic decomposition was investigated, and a feasible mechanism was proposed. The In₂S₃/g-C₃N₄ heterojunctions exhibited the highest photocatalytic degradation when a 40% loading of In₂S₃ was used.184 B. N. R. Winayu et al. enhanced the TiO2 catalyst by introducing sulfur and nitrogen (S, N) components and reduced graphene oxide (rGO) through doping. The most efficient photocatalytic degradation of toluene was achieved using a combination of 1 wt% reduced graphene oxide (rGO) and 0.05 wt% nitrogen-doped titanium dioxide (N_{0.1}TiO₂). 185 V. T. T. Ho et al. stated that the nanostructured Ir-doped TiO2 is a highly effective photocatalyst that produces a superb material for reducing the risk of gaseous toluene. The material had a large surface area and had a consistently spherical shape of 10-15 nm diameter. 186 The composite of PIL (polyionic liquid) a TiO₂ was formed using two different concentrations of polymerized ionic liquid (low and high). The composite was then assessed for its ability to degrade toluene. The findings indicated that the PIL(low)@TiO2 composite exhibited higher activity compared to the PIL(high) @TiO2 composites.187 Z. Sun et al. synthesized a novel hierarchical heterostructured photocatalyst consisting of TiO2/Bi/ Bi₂MoO₆ using a solvothermal technique. On the outermost layer of flower-like Bi₂MoO₆ nanospheres, the TiO₂ nanoparticles were evenly dispersed. The results suggest that the combination of TiO₂ can greatly improve the effectiveness of the photocatalytic oxidation of toluene using the hierarchical heterostructure TiO₂/Bi/Bi₂MoO₆. ¹⁸⁸ Y. Bi et al. used zinc chloride (ZnCl₂), zinc nitrate (Zn(NO₃)₂), and zinc acetate (Zn(CH₃COO)₂)

Table 4 Data fo	Table 4 Data for the catalytic degradation of nitrobenzene using various catalysts	nzene using various o	catalysts			
Nitrobenzene conc. (mg L^{-1}) Catalyst	Catalyst	Catalyst conc. $({ m mg~L}^{-1})$	Operational conditions	Lamp, power (W)	Degradation percentage (%), time (min)	24
50	$\mathrm{SrFeO}_{3-\delta}$	0.001	UV	Mercury vapour, 125	99%, 360	2
50	P-25	I	UV	125	95%, 480	2
40	AuNPs/HPW/TiO ₂ -NTs	I	Visible light	Low-pressure mercury vapor lamp, 15	90%, 30	2
1	Ag/ZnO nanoflowers	I	NN	Tungsten lamp, 60	98%, 100	2
61.5	${ m TiO}_2$	I	Visible light	125	58.46%, 210	2
1	$\mathrm{TiO}_{2}/\mathrm{g}\text{-}\mathrm{C}_{3}\mathrm{N}_{4}/\mathrm{G}$	7.5	an An	Xenon lamp, 300	97%, 240	2
25	H ₃ PW ₁₂ O ₄₀ supported on TiO ₂	10	Visible light	Tungsten light, 500	88%, 390	2
50		I	ΛΩ	Mercury vapor lamp, 200	96%, 240	2
50	TiO_2 -POMs	I	UV		86.4%, 180	2
1900	TiO,-SA-Arg particles	I	UV	UV lamp	93.7%, 120	2

215 216 217 218 219 220 221 222 223 223 224 224

Photocatalyst activation

Introduction of the nitrobenzene

Absorption of the light source

Description of the pollutant

Degraded products

Description of the pollutant

Fig. 4 Working procedure of the photocatalysts for nitrobenzene degradation.

to modify activated carbon fibers (ACFs). Subsequently, titanium dioxide (TiO₂) was loaded onto the modified ACFs. The study found that the photocatalytic performance and adsorption of TiO₂/ACF-Ac modified by Zn(CH₃COO)₂ were highest for the removal of toluene. 189 The presence of a three-dimensional (3D) and directed structure enables efficient absorption of photons and rapid diffusion of volatile organic compounds (VOCs), surpassing the capabilities of catalysts in powder form. The researchers successfully created uniform and free-standing nanowire (NW) arrays of p-type Cu₂O by subjecting Cu(OH)₂ NWs to heat treatment. The Cu₂O NWs, as they are created, exhibit exceptional performance in degrading 30 ppm toluene, with a degradation rate of 99.9% achieved within 120 minutes. 190 P. Mohammadi et al. used a hydrothermal technique to deposit synthesized SrTiO₃ onto graphene oxide (GO). Photocatalysts that were artificially created were utilized for the process of breaking down gaseous toluene dynamically using photocatalysis while being exposed to UV radiation.191 Rostami synthesized a TiO2 and bentonite photocatalyst by a method called co-precipitation and evaluated its catalytic efficiency in degrading para-nitrotoluene (PNT).192 Oxygen vacancies (OVs) can regulate photocatalytic activity by altering their electrical and/or band structures. A wide bandgap p-block metal combination containing OVs, indium oxyhydroxide (InOOH), produced using a one-pot hydrothermal approach, was used to investigate the effect of OVs on photocatalytic decomposition and toluene ring breakage. Validated modified InOOH improves photocatalytic potency by decreasing the energy limitation of critical intermediates for reaction during toluene degradation. 183 X. Zhao et al. enhanced the performance of the C-USTiO2 photocatalyst by applying it to carbon cloth and conducted a study on its ability to continuously degrade toluene under LED light exposure. The results demonstrated that the removal of the degraded toluene can exceed 80% when a large concentration of CO₂ is produced, and it exhibits exceptional cycle stability lasting for over 180 minutes. 193 M. Wu et al. researched the use of CeO2 nanorods for the degradation of toluene using vacuum ultraviolet (VUV) catalytic oxidation. CeO2 nanorods were utilized in a system that involved VUV-photolysis, UV-PCO, OZCO, and UVOZCO processes. Utilizing VUV light instead of ozone catalytic oxidation can significantly enhance the efficiencies, increasing them from 12.9% to 83.2% when combined with the suggested

catalyst. 194 An efficient electrochemical method consisting of two steps was devised to produce a nanotube array of atomically dispersed Au-loaded WO₃/TiO₂ for the oxidation of volatile organic compounds (VOCs). The presence of vacancies (OVs) on the surface of WO₃ greatly improved the separation and movement of photogenerated carriers, as well as the adsorption of toluene. This resulted in an 85.5% mineralization and 95.4% degradation rate for the removal of toluene.195 J. Lyu et al. fabricated a hollow heterophase junction by applying a layer of amorphous TiO2 onto anatase TiO2 hollow spheres. The findings demonstrated that the application of the amorphous TiO2 coating resulted in an augmentation of fine pores and intermediate pores in the photocatalyst, leading to an improved capacity for toluene adsorption.196 By adding nanodiamonds to ZnO, the photocorrosion problem can be solved for photocatalytic degradation of gaseous toluene. A table has been added showing the photocatalytic degradation of toluene Table 3 and Fig. 3 shows the process. Nanodiamond decoration resulted in lowered photoluminescence intensity and electrochemical impedance, enhancing ZnO light absorption, charge transfer, and photocatalytic toluene oxidation efficiency.197

Nitrobenzene

Since aromatic nitro compounds are frequently employed in industrial processes (such as the production of explosives, dyes and insecticides), they are present as contaminants in a variety of liquid sources, particularly surface water, and wastewater from industries.²⁰³ Since nitrobenzene (NB) is identified as a significant contaminant, it is selected as a model pollutant. It is an extremely hazardous material and the highest permitted level of NB is 1 mg L⁻¹ in wastewater.^{204,205} Numerous factors, including the presence of anions, pH, light wavelength, and others, have an impact on nitrobenzene photocatalytic degradation utilizing UV radiation.²⁰⁶ The degradation working mechanism of nitrobenzene in the presence of several photocatalysts is described.^{207,208}

Photocatalyst +
$$h\nu$$
 (photon) \rightarrow Photocatalyst ($e_{cb}^- + h_{\nu b}^+$) (22)

$$e_{cb}^- + O_2 \rightarrow {}^{\bullet}O_2^-$$
 (23)

Nitrobenzene
$$\rightarrow$$
 Catalyst surface (24)

le 5 Data for the catalytic degradation of cyclohexane using various catalysts

Cyclohexane conc.		Catalyst conc.			Degradation percentage	
$(mg L^{-1})$	Catalyst	$(\text{mg } \dot{\text{L}}^{-1})$	Operational conditions	Lamp, power (W)	(%), time (min)	Ref.
200	${ m Pt/TiO_2}$	I	UV, temp: 100 °C with 0.5% Pt loading	Osram Ultra-Vitalux lamp, 300	Close to 100%, —	234
1	${ m Ti}^{3+}$ self-doped ${ m TiO}_2$	I	Visible light, temp: 40 °C	Xenon lamp	95%, 420	235
1	WO ₃ /Co-Pt	100	N	. 1	93%, 720	236
1	Degussa P-25	0.001	Visible light	Metal halide lamp	Around 40%, 180	237
I	WO ₃ -TiO ₂ mixed catalysts	50	Visible light	Xenon lamp, 500	97%, 60	238
I	Au/TiO_2	0.001	Visible light, temp: 25 °C	Mercury lamp, 50	50%, —	239
-	Degussa P25	0.001	UV, temp: 650 °C	Xenon lamp, 450	—, 60	240
523	${ m TiO}_2$	I	UV, temp: 30 °C	Black light lamp, 20	63%, 5	241
-	TiO_2	0.001	UV,—	Mercury lamp, 50	—, 10	239
1	Ag-substituted and	0.001	UV, temp: below 35 $^{\circ}$ C	A high-pressure mercury vapor lamp, 80	Around 10%, 6	242
	impregnated nano- ${ m TiO}_2$					
I	${ m TiO}_2$	I	UV, temp: 140–180 $^{\circ}$ C	A high-pressure mercury lamp, 100	Over 90%, —	243
I	TiO_2	0.001	UV, temp: 60 °C	Medium pressure mercury-vapor lamp, 450	Over 95%, —	244
I	$\mathrm{Na_4W_{10}O_{32}}$	0.05	UV,—	Medium pressure mercury-arc lamp, 125	_, 3	245
1	Fe-modified C-doped Cr ₂ O ₃	1	Visible light, temp: 25 °C	Xenon lamp, 300	_, 5	246

Nitrobenzene + 'OH
$$\rightarrow$$
 Activated nitrobenzene (25)

Activated nitrobenzene + 'OH →

Nitrophenol + Intermediate products (26)

Nitrophenol +
$$OH \rightarrow Degradation products$$
 (27)

Degradation products + 'OH \rightarrow CO₂ + H₂O + Inorganic ions (28)

The study of the impacts of several factors, such as pH, anions, starting concentration, etc., has been done because the rate of breakdown of nitrobenzene utilizing controlled UV radiation is quite significant when compared to that utilizing solar radiation, and a small amount of TiO₂ (0.05%, w/v) was used. 209,210 Degussa P-25 TiO2 was utilized as the photocatalyst in the majority of the nitrobenzene photocatalytic tests. Aldrich-TiO2 (pure anatase with a BET surface area of roughly 250 m² g⁻¹) was used in a few tests.²⁰⁶ Matthews et al. used immobilized TiO2 in a spiral-shaped reactor for the photocatalytic degradation of NB and other chemicals and accomplished around 95-100% degradation at the initial concentration between 1.75 and 4.25 mg L⁻¹.211 Degussa P-25 was applied as the catalyst in photocatalytic degradation tests, and UV lamps with lights radiating at λ_{max} of 253 and 365 nm, respectively, were used. The two bulbs produced nearly identical deterioration.212 When it comes to 4-chlorophenol degradation, it has been discovered that utilizing pulsed photocatalysis makes little distinction in terms of TOC elimination at shorter and longer wavelengths. It should be mentioned that 387 nm is the λ_{min} for anatase TiO_2 .²¹³ The pH has an impact on the ionizable organic molecules' photocatalytic breakdown. The significance of pH on the photocatalytic destruction of NB was assessed within a pH value range of 4-10, in a solution containing 2.52×10^{-4} M of pollutants. The ideal photocatalyst concentration was determined to be 0.5 wt% Fe-TiO2 = 250 mg L⁻¹, with an irradiation period of 60-240 minutes.²¹⁴ A table has been added showing the photocatalytic degradation of nitrobenzene Table 4 and Fig. 4 shows the process. It has been discovered that, given the specified conditions, pH 7 is ideal for NB photocatalytic breakdown.205

Cyclohexane

A common volatile organic compound (VOC) that presents significant dangers to both humans and the environment is cyclohexane.²²⁵ An extremely significant industrial procedure is the breakdown of cyclohexane to produce cyclohexanol and cyclohexanone which are utilized globally as chemical precursors for the synthesis of caprolactam and adipic acid.^{226,227} Photocatalytic techniques for the degradation of cyclohexane in both solid heterogeneous and homogeneous stages have received a lot of research attention in recent years.²²⁸ In heterogeneous environments, semiconductors along with oxides are being used as photocatalysts to oxidize cyclohexane. A number of semiconductors have been used, including CeO₂, WO₃, Sn/Sb, ZrO₂, ZnO, V₂O₅, SnO₂, Sb₂O₄ and mixed oxides.²²⁹ In the presence of various types of photocatalysts, cyclohexane degrades *via* the following mechanism.^{230,231}

Review Nanoscale Advances

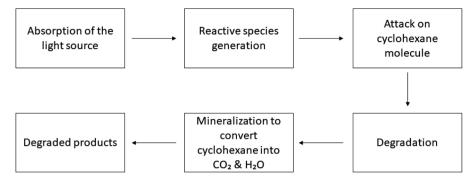


Fig. 5 Working procedure of the photocatalysts for cyclohexane degradation.

Photocatalyst + $h\nu$ (photon) \rightarrow Photocatalyst ($e_{cb}^- + h_{vb}^+$) (29)

$$h_{vb}^{+} + H_2O \rightarrow 'OH + H^+$$
 (30)

$$h_{vh}^{+} + OH^{-} \rightarrow OH$$
 (31)

Cyclohexane +
$$OH \rightarrow Intermediate products$$
 (32)

Intermediate products + 'OH \rightarrow Further degraded products (33)

Intermediate products +
$${}^{\bullet}OH/O_2 \rightarrow$$

 $CO_2 + H_2O + Inorganic ions$ (34)

Xiao et al. discussed the photocatalytic characteristics of silver nanoparticles loaded on the nanocrystals of tungsten oxide when cyclohexane was being photo-catalytically degraded.232 In standard manufacturing processes, cyclohexane is degraded at 150 °C using a homogeneous cobaltbased catalyst.228 Variations in the emitted photon flux and the irradiation wavelength during continuous irradiation result in notable variations in substance outputs and selectivity values during the photocatalytic degradation of cyclohexane by the help of TiO₂ in a pure liquid organic phase.²³³ The photodegradation of cyclohexane proceeded with hydrogen peroxide at ambient temperature, assisted by a copper(II)-exchanged Y zeolite (CuY). A table has been added showing the photocatalytic degradation of cyclohexane Table 5 and Fig. 5 shows the process. Following 6 hours of processing, cyclohexanol and cyclohexyl hydroperoxide with 37% and 54% selectivities, respectively, were obtained as the major products.247

Refinery oil

Several methods may be used for the treatment of oil refinery effluents which include adsorption, Fenton oxidation, electrofloatation-coagulation, photocatalytic degradation/oxidation, chemical flocculation-coagulation, and membrane filtration.²⁴⁸⁻²⁵³ These procedures either produce insignificant impurities or need prolonged durations to eradicate the impurities.²⁵⁴⁻²⁵⁶ Conventional methods like adsorption or membrane separation produce an inferior contaminant by moving the contamination from one phase to another, and the reusability of adsorbents is uncertain. 257,258 Bacterial degradation requires a significant amount of time to break down pollutants and is not suitable for the majority of organic compounds found in oil refinery wastewater. 259-261 Photocatalytic degradation techniques have attracted significant attention due to their ability to break down a wide range of organic compounds utilizing suitable photocatalysts. 52,262,263 The degradation of pollutant chemicals is caused by the hydroxyl radical (OH), which can react with organic compounds and break them down and degrade them.264,265 The mechanism for refinery oil degradation in the presence of various photocatalysts is given.266,267

Photocatalyst + hv (photon) \rightarrow Photocatalyst $(e_{cb}^- + h_{vb}^+)$ (35)

$$e_{cb}^- + O_2 \rightarrow {}^{\bullet}O_2^-$$
 (36)

$$h_{vb}^{+} + H_2O \rightarrow \cdot OH + H^{+}$$
 (37)

$$h_{vb}^{+} + OH^{-} \rightarrow OH$$
 (38)

$$Oil \rightarrow Catalyst surface$$
 (39)

$$Oil + OH \rightarrow Degradation products$$
 (40)

Oil +
$$O_2$$
 \rightarrow Degradation products (41)

Degradation products + 'OH \rightarrow CO₂ + H₂O + Inorganic ions (42)

B. Ogoh-Orch et al. studied BiOI-sensitized TiO₂ (BiOI/ TiO2) nanocomposites with varying amounts of BiOI deposited via sequential ionic layer adsorption and reaction (SILAR) and found that they perform well in water under visible (>400 nm) irradiation for crude oil degradation. The BiOI/TiO2 heterojunction separates photogenerated charges, improving degradation efficiency.268 Actual wastewater from a refinery, containing a variety of aromatic and aliphatic organic compounds, was treated using nanoparticles (specifically TiO2 and ZnO). The degradation ability of the organic contaminants was reduced from 98.57% to 89.482% when the photocatalysts changed from TiO2 to ZnO.267 D. A. Aljuboury et al. investigated the application of ZnO/TiO2/H2O2 using visible

Aromatic compounds = Alkenes = 98.38%, 100

96.04%

Data for the photocatalytic degradation of refinery oil using various catalysts

Table 6

Ref. 268 267 267 269 270 271 272 273 274 275 279 280 281 272 276 278 282 277 Degradation percentage (%), time (min) Oil and grease (OG) =carbon (DOC) = 63% \parallel Oil & grease = 5.2%Dissolved organic **Branched alkanes** IOC = 32% & TNSulfide = 53%, 5 Linear alkanes = Cyclic alkanes = Phenol = 99.9%Phenols = 93%COD = 31.6%over 50%, 60 40.68%, 120 93.92%, 60 85.62, 180 98.57, 120 89.48, 120 66%, 120 90%, 120 78%, 120 76%, 90 88%, 90 67%,90 90%, 4 %99.86 97.31% 83%, **–**, 6 backlight blue bulb, backlight blue bulb, Mercury vapor, 250 Lamp, power (W) Mercury vapor, 6 Fluorescent T8 Fluorescent T8 Mercury, 100 Mercury, 400 Mercury, 150 Mercury, 400 LED, 1000 UV, 400 UV, 400 UV, 11 UV, 11 UV, 60 UV, 8 Visible light, pH 5.5 UV light, pH 3.5-9 UV light, pH 4 UV light, pH 5.5 UV light, pH 5.5 temp: 45 °C O₃/UV, pH 7.16 UV light, pH 7-9 UV light, pH 10 UV light, pH 3, UV light, temp: UV light, pH 3 UV light, pH 3 UV light, pH 4 UV light, pH 3, UV light, pH 6 UV light, pH 4 temp: 45 °C UV, pH = 5Visible light conditions Operation Catalyst conc. 0.0005 - 0.005 $H_2O_2=850$ 0.002-0.008 0.002 - 0.008 $\Gamma iO_2 = 700$ ZnO = 590 (mg L^{-1}) 0.0012 3000 0.001 100 100 100 100 100 100 100 TiO2/ZnO/Degussa TiO₂/ZnO/H₂O₂ TiO₂ in zeolite TiO2/Fe-ZSM-5 Photocatalyst Degussa P25 Degussa P25 BiOI/TiO2 TiO_2 ZnO TiO_2 TiO_2 TiO_2 TiO₂ TiO₂ TiO₂ TiO_2 TiO_2 TiO₂ Oil & grease = 298.8Compound conc. (ppm) Phenol = 0.002Sulfide = 13.3COD = 1954400-600 200-220 15 - 2299.64 0.005 99.64 500 220 70 480 10 | | |Petroleum refinery Petroleum refinery Petroleum refinery Petroleum refinery Petroleum refinery Petroleum refinery **Farget** compound Oil in petroleum Soap oil & grease Refinery oil Refinery oil Refinery oil Refinery oil Refinery oil wastewater wastewater wastewater wastewater wastewater wastewater wastewater Crude oil Crude oil Phenol Phenol Shenol


Table 6 (Contd.)

Target compound	Compound conc. (ppm)	Photocatalyst	Catalyst conc. (mg L^{-1})	Operation conditions	Lamp, power (W)	Degradation percentage (%), time (min)	Ref.
Oil emulsion in distilled/sea water	25	Degussa P25	0.002	UV light, pH 4.5	Mercury, —	In distilled water 92% & in artificial seawater	283
Petroleum refinery wastewater	$\mathrm{COD} = 1326$	Green nanocatalyst from the sepals of	0.00025	UV light, —	uv, —	43.70, 3 99.9%, 90	284
A synthetic oil-water	10 000	TiO ₂	0.002	UV light, —	T8 black light blue	68%, 30	285
Refinery wastewater	100	4-Chlorophenol	178.5	UV light, pH 5	Mercury lamp, 100	—, 80	286

light (1000 W m⁻²), to decrease the total organic carbon (TOC) content in the actual petroleum wastewater obtained from Sohar Refinery Company (SRC). The treatment efficiency for total organic carbon (TOC) at pH 5.5 increased significantly compared to that of the TiO₂ procedure.²⁶⁹ Z. Ghasemi et al. examined the photocatalytic oxidation of organic contaminants in petroleum refinery wastewater (PRWW) utilizing synthesized nano-TiO2 incorporated into Fe-ZSM-5 zeolite and UV light. Results indicate optimal photodegradation efficiency at 3 g L⁻¹ photocatalyst concentration, pH 4, 45 °C temperature, and 120 min UV irradiation.270 Shahrezaei investigated TiO₂ photocatalysis for the primary degradation of phenol and phenolic compounds in refinery wastewater. Under optimal conditions, 90% phenol removal was achieved in 2 hours.²⁷¹ The user created a composite membrane by combining polyvinylidene and titanium dioxide (PVDF/TiO2) and then treated it using the hot-pressing method. A table has been added showing the photocatalytic degradation of cyclohexane Table 6 and Fig. 6 shows the process. This treatment was done to increase the bonding between the TiO2 and the membrane surfaces, to employ the membrane to degrade oil in wastewater.

Effects of crystal size and surface area on photocatalytic degradation

Organic chemicals and the photocatalyst's surface coverage are directly correlated, and therefore surface morphology, such as crystal size and the surface area, must be taken into account during the photocatalytic degradation procedure. 287,288 Since every chemical process occurs at the surface, the surface morphology of any photocatalyst is essential to its efficacy as a catalyst.289 The anatase phase with a range of 2.59 to 12.00 nm in TiO₂ crystallite dimensions is visible in metal-doped TiO₂ products. TiO2 has a specific surface area of between 100 and 500 m² g⁻¹. ^{290,291} Sivalingam *et al.* used a solution combustion process where 8-10 nm pure anatase phase TiO₂ with 156 m² g⁻¹ BET surface area was created. This TiO₂ is commonly utilized for photocatalytic degradation of many dyes, including Orange G, Methylene Blue, Alizarin S, Methyl Red, and Congo Red. In this analysis, the crystal size of the photocatalyst was found to be 8 ± 2 nm.²⁹² The photoactivity of the photocatalysts increased due to the higher surface area. It has been found that the photoactivity of the TiO2 while degrading the dye-like MB increased when the surface area of the catalyst increased from 63 m² g⁻¹ to 156 m² g⁻¹. For the maximum degradation of antibiotics like cefoxitin sodium, a novel BN/CdAl₂O₄ composite with a surface area of 14.34 m² g⁻¹ is used.¹³³ Mushtaq et al. found a decrease in the degradation rate of the ofloxacin antibiotic due to the increase in the particle size and decrease in the surface area of the photocatalysts.²⁹⁴ The same scenario was also found during the advanced degradation of tetracycline antibiotics by graphene-ordered mesoporous silica.295 Zhou et al. used highly photoactive mesoporous anatase nanospheres that have a high specific surface area of 609 m² g⁻¹ for the degradation of toluene.296 The highest specific surface area (130.3 m² g⁻¹) of Nanoscale Advances

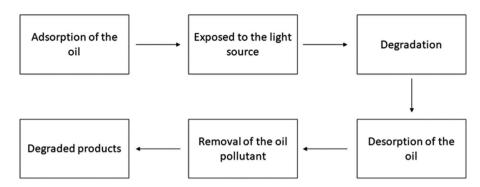

Working procedure of the photocatalysts for refinery oil degradation.

nano-sized TiO2 particles synthesized under ideal conditions is almost double that of Degussa P25 which is used for toluene degradation.297 R. J. Tayade et al. experimented with the degradation of nitrobenzene using nanocrystalline TiO2 of different surface areas, i.e. 259/199/166/124/91/2 m² g⁻¹.216 Photocatalytic oxidation of cyclohexane over TiO₂ nanoparticles by molecular oxygen was carried out using different surface area photocatalysts ranging between 30 and 410 m² g⁻¹.²⁹⁸ TiO₂ is made up of anatase and rutile with a mean particle size of 30 nm and a surface area of 50 m² g⁻¹ for the maximum degradation of refinery oil.285

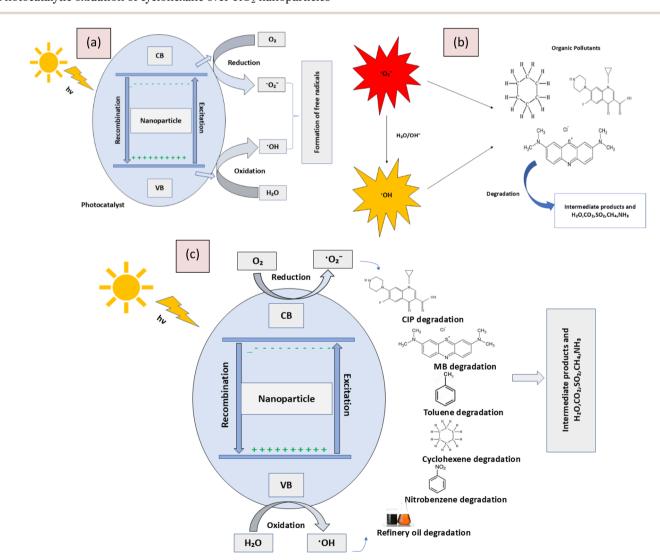


Fig. 7 Illustration of (a) formation of free radicals, (b) degradation of the organic pollutants by radicals, and (c) overall photocatalytic degradation mechanism.

Review Nanoscale Advances

Mechanism of photocatalytic degradation

Photocatalytic degradation is a process where light energy, typically from UV or visible light, activates a photocatalyst, such as titanium dioxide (TiO₂). When the photocatalyst absorbs light, it generates electron-hole pairs. These electron-hole pairs can initiate redox reactions that produce reactive oxygen species (ROS) like hydroxyl radicals and superoxide anions. These ROS are highly reactive and can break down organic pollutants, converting them into less harmful substances like water, carbon dioxide, and inorganic ions. The overall mechanism involves light absorption, generation of electron-hole pairs, formation of ROS, and degradation of pollutants (Fig. 7).

Conclusion

Various photocatalysts are used depending on the variation in organic pollutants. Titanium dioxide (TiO2) is the most broadly applied photocatalyst, known for its maximum ability, stability, and non-toxicity. It is primarily activated by UV light. Zinc oxide (ZnO) is another effective photocatalyst with properties similar to those of TiO2 but with some advantages under certain conditions. Recent research includes materials like cadmium sulfide (CdS), tungsten oxide (WO₃), and various metal-organic frameworks (MOFs) as effective photocatalysts. Scientists are working on photocatalysts that are triggered by visible light in order to improve the process's applicability and reduce energy consumption in the real world. This review scrutinizes the variance in the degradation rate of organic pollutants under different conditions such as different pH levels, different concentration levels, various composites of the photocatalysts, different surface areas and sizes of the photocatalysts, and so on. This review will help to identify the optimum parameters for the maximum amount of organic pollutant degradation. The goal of this field's ongoing research and development is to broaden the use of catalytic technologies and overcome current obstacles to ensure cleaner soil and water thus leading to a more sustainable environment. Greater prospects for the use of photocatalysis in the destruction of dangerous organic pollutants may arise from a greater understanding of the process and its operating parameters.

Data availability

Data will be made available on request.

Author contributions

Abdullah Al Miad and Shassatha Paul Saikat collected the data and wrote the draft and original manuscript. Md. Sahadat Hossain conceived and designed the review, analyzed the data, and assisted in writing the manuscript. Md. Kawcher Alam assisted in collecting data. Newaz Mohammed Bahadur and Samina Ahmed supervised the findings of this work. Samina Ahmed supervised the overall work and managed the required facilities.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors are grateful to the Bangladesh Council of Scientific and Industrial Research (BCSIR) authority for financial support through the R&D project (ref. no. 39.02.0000.011.14.134.2021/900; date: 30.12.2021). Abdullah Al Miad wishes to thank the Department of Applied Chemistry and Chemical Engineering, Noakhali Science and Technology University, Noakhali.

References

- 1 J. Levec and A. Pintar, Catal. Today, 2007, 124, 172-184.
- 2 J. Umamaheswari and S. Shanthakumar, Rev. Environ. Sci. Biotechnol., 2016, 15, 265–284.
- 3 M. Molinos-Senante, R. Sala-Garrido and F. Hernández-Sancho, *J. Cleaner Prod.*, 2016, **112**, 3116–3123.
- 4 B. S. Patel, B. R. Solanki and A. U. Mankad, *World J. Adv. Res. Rev.*, 2021, **10**, 323–333.
- 5 I. Angelidaki, A. S. Mogensen and B. K. Ahring, *Biodegradation*, 2000, **11**, 377–383.
- 6 P. Kaszycki, M. Głodniok and P. Petryszak, *New Biotechnol.*, 2021, **61**, 80–89.
- 7 A. P. Bhat and P. R. Gogate, J. Hazard. Mater., 2021, 403, 123657.
- 8 B. S. Rathi, P. S. Kumar and D.-V. N. Vo, *Sci. Total Environ.*, 2021, 797, 149134.
- 9 H. F. Stroo, J. Environ. Qual., 1992, 21, 167-175.
- 10 S. Krishnan, H. Rawindran, C. M. Sinnathambi and J. W. Lim, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2017, **206**, 012089.
- 11 T. A. Kurniawan, G. Y. Chan, W.-H. Lo and S. Babel, *Chem. Eng. J.*, 2006, **118**, 83–98.
- 12 M. Ahmaruzzaman, *Adv. Colloid Interface Sci.*, 2011, **166**, 36–59.
- 13 I. Ali, M. Asim and T. A. Khan, *J. Environ. Manage.*, 2012, **113**, 170–183.
- 14 D. Chatterjee and S. Dasgupta, J. Photochem. Photobiol., C, 2005, 6, 186–205.
- 15 V. Vinayagam, K. N. Palani, S. Ganesh, S. Rajesh, V. V. Akula, R. Avoodaiappan, O. S. Kushwaha and A. Pugazhendhi, *Environ. Res.*, 2023, 117500.
- 16 M. M. Ali, D. Hossain, A. Al-Imran, M. S. Khan, M. Begum and M. H. Osman, *Heavy Metals - Their Environmental Impacts and Mitigation*, 2021, pp. 771–783.
- 17 T. Encarnação, A. A. Pais, M. G. Campos and H. D. Burrows, *Sci. Prog.*, 2019, **102**, 3–42.
- 18 N. Gaur, K. Narasimhulu and Y. PydiSetty, *J. Cleaner Prod.*, 2018, **198**, 1602–1631.
- 19 L. Wang, D. Luo, O. Hamdaoui, Y. Vasseghian, M. Momotko, G. Boczkaj, G. Z. Kyzas and C. Wang, Sci. Total Environ., 2023, 876, 162551.

Nanoscale Advances

- 20 W. H. Glaze and J. Kang, J. AWWA, 1988, 80, 57-63.
- 21 W. H. Glaze, J.-W. Kang and D. H. Chapin, Ozone: Sci. Eng., 1987, 9, 335-352.
- 22 H. Liu, X. Li, X. Zhang, F. Coulon and C. Wang, Chemosphere, 2023, 139404.
- 23 A. Cesaro, V. Naddeo and V. Belgiorno, J. Biorem. Biodegrad., 2013, 4, 1-8.
- 24 K. Ayoub, E. D. Van Hullebusch, M. Cassir and A. Bermond, J. Hazard. Mater., 2010, 178, 10-28.
- 25 M. N. Chong, B. Jin, C. W. Chow and C. Saint, Water Res., 2010, 44, 2997-3027.
- 26 H. M. Coleman, C. P. Marquis, J. A. Scott, S.-S. Chin and R. Amal, Chem. Eng. J., 2005, 113, 55-63.
- 27 R. Comparelli, E. Fanizza, M. L. Curri, P. D. Cozzoli, G. Mascolo and A. Agostiano, Appl. Catal., B, 2005, 60, 1-11.
- 28 D. Zhu and Q. Zhou, Environ. Nanotechnol., Monit. Manage., 2019, 12, 100255.
- 29 K. M. Reza, A. Kurny and F. Gulshan, Appl. Water Sci., 2017, 7, 1569-1578.
- 30 K. Nakata and A. Fujishima, J. Photochem. Photobiol., C, 2012, 13, 169-189.
- 31 A. Y. Nosaka, E. Kojima, T. Fujiwara, H. Yagi, H. Akutsu and Y. Nosaka, J. Phys. Chem. B, 2003, 107, 12042-12044.
- 32 A. G. Agrios and P. Pichat, J. Appl. Electrochem., 2005, 35, 655-663.
- 33 Y. Wicaksana, S. Liu, J. Scott and R. Amal, Molecules, 2014, 19, 17747-17762.
- 34 S. Ramanavičius, M. Petrulevičienė, J. Juodkazytė, A. Grigucevičienė and A. Ramanavičius, Materials, 2020, 13, 523.
- 35 V. K. Vidhu and D. Philip, *Micron*, 2014, **56**, 54–62.
- 36 F. Kiriakidou, D. I. Kondarides and X. E. Verykios, Catal. Today, 1999, 54, 119-130.
- 37 M. Umar and H. A. Aziz, Org. Pollut.: Monit., Risk Treat., 2013, 8, 196-197.
- 38 A. Bumajdad and M. Madkour, Phys. Chem. Chem. Phys., 2014, 16, 7146-7158.
- 39 M. Sleiman, D. Vildozo, C. Ferronato and J.-M. Chovelon, Appl. Catal., B, 2007, 77, 1-11.
- 40 R. S. Thakur, R. Chaudhary and C. Singh, J. Renewable Sustainable Energy, 2010, 2, 42701.
- 41 M. R. D. Khaki, M. S. Shafeeyan, A. A. A. Raman and W. M. A. W. Daud, J. Environ. Manage., 2017, 198, 78-94.
- 42 E. Rosales, M. Pazos, M. A. Longo and M. A. Sanromán, J. Environ. Sci. Health, Part A: Toxic/Hazard. Subst. Environ. Eng., 2009, 44, 1104-1110.
- 43 L. Corra, J. Health Pollut., 2018, 8, 180916.
- 44 D. Montes-Grajales, M. Fennix-Agudelo and W. Miranda-Castro, Sci. Total Environ., 2017, 595, 601-614.
- 45 K. Vassilev and V. Kambourova, in Chemicals as Intentional and Accidental Global Environmental Threats, ed. L. Simeonov and E. Chirila, Springer Netherlands, Dordrecht, 2006, pp. 173-191.
- 46 R. Naidu, B. Biswas, I. R. Willett, J. Cribb, B. K. Singh, C. P. Nathanail, F. Coulon, K. T. Semple, K. C. Jones and A. Barclay, Environ. Int., 2021, 156, 106616.

47 V. Vinayagam, K. N. Palani, S. Ganesh, S. Rajesh, V. V. Akula, R. Avoodaiappan, O. S. Kushwaha and A. Pugazhendhi, Environ. Res., 2023, 117500.

- 48 R. Gothwal and T. Shashidhar, Clean: Soil, Air, Water, 2015, 43, 479-489.
- 49 S. Benkhaya, S. M'rabet, H. Lgaz, A. El Bachiri and A. El Harfi, in Dye Biodegradation, Mechanisms and Techniques, ed. S. S. Muthu and A. Khadir, Springer Singapore, Singapore, 2022, pp. 1-50.
- 50 A. Abatan, A. Obaigbena, E. D. Ugwuanyi, B. S. Jacks, U. J. Umoga, O. H. Daraojimba and O. A. Lottu, J. Eng. Sci. Technol., 2024, 5, 543-554.
- 51 S. S. Shetty, S. Sonkusare, P. B. Naik and H. Madhyastha, Heliyon, 2023, 9, E19496.
- 52 D. Chen, Y. Cheng, N. Zhou, P. Chen, Y. Wang, K. Li, S. Huo, P. Cheng, P. Peng and R. Zhang, J. Cleaner Prod., 2020, 268, 121725.
- 53 A. Ucar, M. Findik, I. H. Gubbuk, N. Kocak and H. Bingol, Mater. Chem. Phys., 2017, 196, 21-28.
- 54 U. Kurtan, A. Baykal and H. Sözeri, J. Inorg. Organomet. Polym. Mater., 2015, 25, 921-929.
- 55 K. Yu, S. Yang, C. Liu, H. Chen, H. Li, C. Sun and S. A. Boyd, Environ. Sci. Technol., 2012, 46, 7318-7326.
- 56 M.-C. Roşu, C. Socaci, V. Floare-Avram, G. Borodi, F. Pogăcean, M. Coroș, L. Măgerușan and S. Pruneanu, Mater. Chem. Phys., 2016, 179, 232-241.
- 57 H. Kumari, S. Sonia, R. Ranga, S. Chahal, S. Devi, S. Sharma, S. Kumar, P. Kumar, S. Kumar, A. Kumar and R. Parmar, Water, Air, Soil Pollut., 2023, 234, 349.
- 58 J. H. B. Pinton, A. F. Oliveira, D. R. Huanca and N. D. Mohallem, Mater. Chem. Phys., 2024, 129213.
- 59 M. F. Lanjwani, M. Tuzen, M. Y. Khuhawar and T. A. Saleh, Inorg. Chem. Commun., 2024, 159, 111613.
- 60 S. Xia, L. Zhang, G. Pan, P. Qian and Z. Ni, Phys. Chem. Chem. Phys., 2015, 17, 5345-5351.
- 61 M. K. Alam, M. S. Hossain, S. Tabassum, N. M. Bahadur and S. Ahmed, Open Ceram., 2024, 19, 100625.
- 62 C. Hu, C. Y. Jimmy, Z. Hao and P. K. Wong, Appl. Catal., B, 2003, 46, 35-47.
- 63 J. Zhang, B. Tian, L. Wang, M. Xing and J. Lei, Photocatalysis: Fundamentals, Materials and Applications, Springer Singapore, Singapore, 2018, vol. 100, pp. 1-49.
- 64 R. Velmurugan and M. Swaminathan, Sol. Energy Mater. Sol. Cells, 2011, 95, 942-950.
- 65 M. H. Elsayed, T. M. Elmorsi, A. M. Abuelela, A. E. Hassan, A. Z. Alhakemy, M. F. Bakr and H.-H. Chou, J. Taiwan Inst. Chem. Eng., 2020, 115, 187-197.
- 66 L.-Y. Yang, S.-Y. Dong, J.-H. Sun, J.-L. Feng, Q.-H. Wu and S.-P. Sun, J. Hazard. Mater., 2010, 179, 438-443.
- 67 N. Sobana and M. Swaminathan, Sol. Energy Mater. Sol. Cells, 2007, 91, 727-734.
- 68 C. M. So, M. Y. Cheng, J. C. Yu and P. K. Wong, Chemosphere, 2002, 46, 905-912.
- 69 S. K. Kansal, N. Kaur and S. Singh, Nanoscale Res. Lett., 2009, 4, 709.
- 70 H. Liang, X. Li, Y. Yang and K. Sze, Chemosphere, 2008, 73, 805-812.

71 R. Singh and S. Dutta, Nano-Struct. Nano-Objects, 2019, 18,

- 100250.
- 72 T. Torimoto, S. Ito, S. Kuwabata and H. Yoneyama, *Environ. Sci. Technol.*, 1996, **30**, 1275–1281.
- 73 N. Takeda, T. Torimoto, S. Sampath, S. Kuwabata and H. Yoneyama, *J. Phys. Chem.*, 1995, **99**, 9986–9991.
- 74 I. Poulios, A. Avranas, E. Rekliti and A. Zouboulis, *J. Chem. Technol. Biotechnol.*, 2000, 75, 205–212.
- 75 W.-Y. Wang and Y. Ku, Colloids Surf., A, 2007, 302, 261-268.
- 76 K. Bubacz, J. Choina, D. Dolat and A. W. Morawski, *Pol. J. Environ. Stud.*, 2010, **19**, 685–691.
- 77 B. Neppolian, H. C. Choi, S. Sakthivel, B. Arabindoo and V. Murugesan, *Chemosphere*, 2002, **46**, 1173–1181.
- 78 K. Tanaka, K. Padermpole and T. Hisanaga, *Water Res.*, 2000, **34**, 327–333.
- 79 N. Daneshvar, D. Salari and A. R. Khataee, *J. Photochem. Photobiol.*, *A*, 2003, **157**, 111–116.
- 80 V. Augugliaro, C. Baiocchi, A. B. Prevot, E. García-López, V. Loddo, S. Malato, G. Marcí, L. Palmisano, M. Pazzi and E. Pramauro, *Chemosphere*, 2002, 49, 1223–1230.
- 81 M. Saquib and M. Muneer, Dyes Pigm., 2003, 56, 37-49.
- 82 I. K. Konstantinou and T. A. Albanis, *Appl. Catal., B*, 2004, **49**, 1–14.
- 83 V.-H. Nguyen, S. D. Lin, J. C.-S. Wu and H. Bai, *Beilstein J. Nanotechnol.*, 2014, 5, 566–576.
- 84 D. F. Ollis, E. Pelizzetti and N. Serpone, *Environ. Sci. Technol.*, 1991, **25**, 1522–1529.
- 85 C.-H. Hung and C. Yuan, *J. Chin. Inst. Environ. Eng.*, 2000, **10**, 209–216.
- 86 K. V. S. Rao, M. Subrahmanyam and P. Boule, *Appl. Catal.*, B, 2004, 49, 239–249.
- 87 E. T. Soares, M. A. Lansarin and C. C. Moro, *Braz. J. Chem. Eng.*, 2007, **24**, 29–36.
- 88 R. Ullah and J. Dutta, J. Hazard. Mater., 2008, 156, 194-200.
- 89 A. Salama, A. Mohamed, N. M. Aboamera, T. A. Osman and A. Khattab, *Appl. Nanosci.*, 2018, **8**, 155–161.
- 90 H. A. Kiwaan, T. M. Atwee, E. A. Azab and A. A. El-Bindary, J. Mol. Struct., 2020, 1200, 127115.
- 91 G. Annadurai, T. Sivakumar and S. Rajesh Babu, *Bioprocess Eng.*, 2000, 23, 167–173.
- 92 S. Sriram, K. C. Lalithambika and A. Thayumanavan, *Optik*, 2017, **139**, 299–308.
- 93 M. Zhou, X. Tian, H. Yu, Z. Wang, C. Ren, L. Zhou, Y.-W. Lin and L. Dou, *ACS Omega*, 2021, **6**, 26439–26453.
- 94 I. N. Reddy, C. V. Reddy, J. Shim, B. Akkinepally, M. Cho, K. Yoo and D. Kim, *Catal. Today*, 2020, 340, 277–285.
- 95 R. Saravanan, H. Shankar, G. Rajasudha, A. Stephen and V. Narayanan, *Int. J. Nanosci.*, 2011, **10**, 253–257.
- 96 C. Xu, L. Cao, G. Su, W. Liu, H. Liu, Y. Yu and X. Qu, *J. Hazard. Mater.*, 2010, **176**, 807–813.
- 97 A. Mohammad, K. Kapoor and S. M. Mobin, *ChemistrySelect*, 2016, 1, 3483–3490.
- 98 F. Li, S. Sun, Y. Jiang, M. Xia, M. Sun and B. Xue, *J. Hazard. Mater.*, 2008, **152**, 1037–1044.
- 99 E. S. Al-Farraj, M. Khairy, F. A. Saad, R. K. Shah and E. A. Abdelrahman, *Water Conserv. Sci. Eng.*, 2024, **9**, 3.

- 100 B. Haspulat Taymaz, M. Demir, H. Kamış, H. Orhan, Z. Aydoğan and A. Akıllı, *Int. J. Phytorem.*, 2023, **25**, 1306–1317.
- 101 N. Madima, K. K. Kefeni, S. B. Mishra and A. K. Mishra, *Heliyon*, 2022, **8**, e10683.
- 102 J.-P. Dong, Z.-Z. Shi, B. Li and L.-Y. Wang, *Dalton Trans.*, 2019, **48**, 17626–17632.
- 103 X. Xue, W. Zang, P. Deng, Q. Wang, L. Xing, Y. Zhang and Z. L. Wang, *Nano Energy*, 2015, 13, 414–422.
- 104 S. Thirumalairajan, K. Girija, V. R. Mastelaro and N. Ponpandian, *New J. Chem.*, 2014, 38, 5480–5490.
- 105 K. Byrappa, A. K. Subramani, S. Ananda, K. M. L. Rai, R. Dinesh and M. Yoshimura, *Bull. Mater. Sci.*, 2006, 29, 433–438.
- 106 C.-Y. Chen, Water, Air, Soil Pollut., 2009, 202, 335-342.
- 107 Z. Shan, W. Wang, X. Lin, H. Ding and F. Huang, J. Solid State Chem., 2008, 181, 1361–1366.
- 108 S. Zhou and A. K. Ray, *Ind. Eng. Chem. Res.*, 2003, **42**, 6020–6033.
- 109 K. Mehrotra, G. S. Yablonsky and A. K. Ray, *Chemosphere*, 2005, **60**, 1427–1436.
- 110 M. Sharma, D. Rajput, V. Kumar, I. Jatain, T. M. Aminabhavi, G. Mohanakrishna, R. Kumar and K. K. Dubey, *Environ. Res.*, 2023, 231, 116132.
- 111 T. D. Nguyen, T. Lee, T. Van Tran, V. H. Nguyen, L. X. Nong, L. G. Bach and D.-V. N. Vo, *Environ. Chem. Lett.*, 2023, 21, 935–980.
- 112 H. Khurshid, Z. Mehmood, S. Naseer, M. Aamir, F. Khurshid and M. Khan, *Pak. J. Biochem. Mol. Biol.*, 2023, **56**, 117–128.
- 113 B. Zhang, R. Xu, Y. Feng and J. Wang, *Ionics*, 2024, **30**, 1291–1306.
- 114 W. Hu, Y. Zhang, B. Huang and Y. Teng, *Chemosphere*, 2017, **170**, 183–195.
- 115 S. Shen, Y. Huang, A. Yuan, F. Lv, L. Liu and S. Wang, *CCS Chem.*, 2021, 3, 129–135.
- 116 Z.-Y. Lu, Y.-L. Ma, J.-T. Zhang, N.-S. Fan, B.-C. Huang and R.-C. Jin, *J. Water Process Eng.*, 2020, **38**, 101681.
- 117 M. S. De Ilurdoz, J. J. Sadhwani and J. V. Reboso, *J. Water Process Eng.*, 2022, 45, 102474.
- 118 B. L. Phoon, C. C. Ong, M. S. Mohamed Saheed, P.-L. Show, J.-S. Chang, T. C. Ling, S. S. Lam and J. C. Juan, *J. Hazard. Mater.*, 2020, 400, 122961.
- 119 Z. Derakhshan, M. Mokhtari, F. Babaei, R. M. Ahmadi, M. H. Ehrampoush and M. Faramarzian, *J. Environ. Health Sustainable Dev.*, 2016, 1, 43–62.
- 120 X. Bai, W. Chen, B. Wang, T. Sun, B. Wu and Y. Wang, *Int. J. Mol. Sci.*, 2022, 23, 8130.
- 121 Y. Chen, J. Yang, L. Zeng and M. Zhu, *Crit. Rev. Environ. Sci. Technol.*, 2022, **52**, 1401–1448.
- 122 R. Ebrahimi, A. Maleki, Y. Zandsalimi, R. Ghanbari, B. Shahmoradi, R. Rezaee, M. Safari, S. W. Joo, H. Daraei, S. Harikaranahalli Puttaiah and O. Giahi, *J. Ind. Eng. Chem.*, 2019, 73, 297–305.
- 123 T. C. M. V. Do, D. Q. Nguyen, K. T. Nguyen and P. H. Le, *Materials*, 2019, **12**, 2434.

Nanoscale Advances Review

- 124 K. O'Dowd, K. M. Nair and S. C. Pillai, Curr. Opin. Green Sustainable Chem., 2021, 30, 100471.
- 125 K. Rokesh, M. Sakar and T.-O. Do, Nanomaterials, 2021, 11, 572.
- 126 X. Hu, X. Hu, Q. Peng, L. Zhou, X. Tan, L. Jiang, C. Tang, H. Wang, S. Liu and Y. Wang, Chem. Eng. J., 2020, 380, 122366.
- 127 Z. Yang, J. Yan, J. Lian, H. Xu, X. She and H. Li, ChemistrySelect, 2016, 1, 5679-5685.
- 128 M. Verma and A. K. Haritash, Environ. Technol. Innovation, 2020, 20, 101072.
- 129 Q. Zhang, L. Jiang, J. Wang, Y. Zhu, Y. Pu and W. Dai, Appl. Catal., B, 2020, 277, 119122.
- 130 G. Fan, H. Peng, J. Zhang, X. Zheng, G. Zhu, S. Wang and L. Hong, Catal. Sci. Technol., 2018, 8, 5906-5919.
- 131 F. Torki and H. Faghihian, J. Photochem. Photobiol., A, 2017, 338, 49-59.
- 132 A. Payan, A. Akbar Isari and N. Gholizade, Chem. Eng. J., 2019, 361, 1121-1141.
- 133 R. Kumar, M. A. Barakat, B. A. Al-Mur, F. A. Alseroury and J. O. Eniola, J. Cleaner Prod., 2020, 246, 119076.
- 134 T. Senasu, T. Chankhanittha, K. Hemavibool and S. Nanan, Catal. Today, 2022, 384-386, 209-227.
- 135 Y. Gong, Y. Wu, Y. Xu, L. Li, C. Li, X. Liu and L. Niu, Chem. Eng. J., 2018, 350, 257-267.
- 136 W. Wang, Q. Han, Z. Zhu, L. Zhang, S. Zhong and B. Liu, Adv. Powder Technol., 2019, 30, 1882-1896.
- 137 N. Askari, M. Beheshti, D. Mowla and M. Farhadian, Mater. Sci. Semicond. Process., 2021, 127, 105723.
- 138 A. Mohammad, M. E. Khan, M. H. Cho and T. Yoon, Appl. Surf. Sci., 2021, 565, 150337.
- 139 M. Berkani, A. Smaali, Y. Kadmi, F. Almomani, Y. Vasseghian, N. Lakhdari and M. Alyane, J. Hazard. Mater., 2022, 421, 126719.
- 140 H. Bouyarmane, C. El Bekkali, J. Labrag, I. Es-saidi, O. Bouhnik, H. Abdelmoumen, A. Laghzizil, J.-M. Nunzi and D. Robert, Surf. Interfaces, 2021, 24, 101155.
- 141 F. Guo, X. Huang, Z. Chen, L. Cao, X. Cheng, L. Chen and W. Shi, Sep. Purif. Technol., 2021, 265, 118477.
- 142 M. Abdullah, J. Iqbal, M. S. Ur Rehman, U. Khalid, F. Mateen, S. N. Arshad, A. G. Al-Sehemi, H. Algarni, O. A. Al-Hartomy and T. Fazal, Chemosphere, 2023, 317, 137834.
- 143 T. Chankhanittha and S. Nanan, J. Colloid Interface Sci., 2021, 582, 412-427.
- 144 L. Liu, J. Huang, H. Yu, J. Wan, L. Liu, K. Yi, W. Zhang and C. Zhang, Chemosphere, 2021, 282, 131049.
- 145 E. Gómez, R. Cestaro, L. Philippe and A. Serrà, Appl. Catal., B, 2022, 317, 121703.
- 146 P. Gholami, A. Khataee, R. D. C. Soltani, L. Dinpazhoh and A. Bhatnagar, J. Hazard. Mater., 2020, 382, 121070.
- 147 T. Xiao, Z. Tang, Y. Yang, L. Tang, Y. Zhou and Z. Zou, Appl. Catal., B, 2018, 220, 417-428.
- 148 Y. Sneha, S. R. Yashas, T. Thinley, S. Prabagar Jijoe and H. Puttaiah Shivaraju, Environ. Sci. Pollut. Res., 2022, 29, 67969-67980.

- 149 J. Wang, W. Liu, D. Zhong, Y. Ma, Q. Ma, Z. Wang and J. Pan, J. Mater. Sci., 2019, 54, 13740-13752.
- 150 M. Shokri, G. Isapour, M. A. Behnajady and S. Dorosti, Desalin. Water Treat., 2016, 57, 12874-12881.
- 151 M. N. Abellán, J. Giménez and S. Esplugas, Catal. Today, 2009, 144, 131-136.
- 152 N. P. Xekoukoulotakis, C. Drosou, C. Brebou, E. Chatzisymeon, E. Hapeshi, D. Fatta-Kassinos and D. Mantzavinos, Catal. Today, 2011, 161, 163-168.
- 153 A. L. Giraldo, G. A. Penuela, R. A. Torres-Palma, N. J. Pino, R. A. Palominos and H. D. Mansilla, Water Res., 2010, 44, 5158-5167.
- 154 M. Chen and W. Chu, *J. Hazard. Mater.*, 2012, **219**, 183–189.
- 155 P. Huo, X. Gao, Z. Lu, X. Liu, Y. Luo, W. Xing, J. Li and Y. Yan, Desalin. Water Treat., 2014, 52, 6985-6995.
- 156 A. Chatzitakis, C. Berberidou, I. Paspaltsis, G. Kyriakou, T. Sklaviadis and I. Poulios, Water Res., 2008, 42, 386-394.
- 157 M. N. Abellán, B. Bayarri, J. Giménez and J. Costa, Appl. Catal., B, 2007, 74, 233-241.
- 158 M. Pascal, L. Pascal, M.-L. Bidondo, A. Cochet, H. Sarter, M. Stempfelet and V. Wagner, J. Environ. Public Health, 2013, 2013, 1-17.
- 159 S. N. Shah, Pak. J. Sci., 2016, 29, 701-706.
- 160 F. A. Kuranchie, P. N. Angnunavuri, F. Attiogbe and E. N. Nerquaye-Tetteh, Cogent Environ. Sci., 2019, 5, 1603418.
- 161 Y. Liu, M. Shao, L. Fu, S. Lu, L. Zeng and D. Tang, Atmos. Environ., 2008, 42, 6247-6260.
- 162 V. O. N. Njoku, C. Arinze, I. F. Chizoruo and E. N. Blessing, Anal. Methods Environ. Chem. J., 2021, 4, 80-106.
- 163 J. E. Idomeh, O. B. Shittu, J. A. Oyedepo, B. S. Bada, S. A. Balogun, F. A. Idomeh and R. S. Ezenweani, Geomicrobiol. J., 2021, 38, 879-894.
- 164 C.-H. Hsu, T. Stedeford, E. Okochi-Takada, T. Ushijima, H. Noguchi, C. Muro-Cacho, J. W. Holder and M. Banasik, J. Environ. Sci. Health, Part C: Environ. Carcinog. Ecotoxicol. Rev., 2007, 25, 155-184.
- 165 S. Kuppusamy, N. R. Maddela, M. Megharaj and K. Venkateswarlu, in Total Petroleum Hydrocarbons, Springer International Publishing, Cham, 2020, pp. 95-138.
- 166 R. Gusain, K. Gupta, P. Joshi and O. P. Khatri, Adv. Colloid Interface Sci., 2019, 272, 102009.
- 167 D. Murindababisha, A. Yusuf, Y. Sun, C. Wang, Y. Ren, J. Lv, H. Xiao, G. Z. Chen and J. He, Environ. Sci. Pollut. Res., 2021, 28, 62030-62060.
- 168 A. N. Ozogu, O. F. Opeoluwa, A. A. Olusegun, S. O. Adegboyega and S. O. Michael, J. Innovative Res., 2023, 1, 4-11.
- 169 W. Zou, B. Gao, Y. S. Ok and L. Dong, Chemosphere, 2019, 218, 845-859.
- 170 X. Yang and I. Khan, Environ. Sci. Pollut. Res., 2022, 29, 4116-4127.
- 171 E. Rehman and S. Rehman, Energy Rep., 2022, 8, 5430-5442.
- 172 M. D. Holmes and B. P. Murray. Toluene Toxicity, in StatPearls [Internet], StatPearls Publishing, Treasure

Island (FL), 2024, Available from: https://www.ncbi.nlm.nih.gov/books/NBK599523/.

- 173 A. Hartwig, M. Arand and M. A. K. Commission, *MAK-Collection of Occupational Health and Safety*, 2023, 8, 1–38.
- 174 G. Pelletti, in *Handbook of Substance Misuse and Addictions*, ed. V. B. Patel and V. R. Preedy, Springer International Publishing, Cham, 2022, pp. 2591–2609.
- 175 M. V. Soares, J. Mesadri, D. F. Gonçalves, L. M. Cordeiro, A. F. da Silva, F. B. O. Baptista, R. Wagner, C. L. Dalla Corte, F. A. A. Soares and D. S. Ávila, *Environ. Pollut.*, 2022, 298, 118856.
- 176 M. F. Mohammad, L. Y. Mousa, D. H. Idayyir and Z. M. Kadim, *Teikyo Med. J.*, 2021, 44, 3345–3353.
- 177 G. Izydorczyk, K. Mikula, D. Skrzypczak, K. Moustakas, A. Witek-Krowiak and K. Chojnacka, *Environ. Res.*, 2021, 197, 111050.
- 178 Y. Barwise and P. Kumar, npj Clim. Atmos. Sci., 2020, 3, 12.
- 179 E. Nemitz, M. Vieno, E. Carnell, A. Fitch, C. Steadman, P. Cryle, M. Holland, R. D. Morton, J. Hall and G. Mills, *Philos. Trans. R. Soc.*, *A*, 2020, 378, 20190320.
- 180 A. Roy, A. Sharma, S. Yadav, L. T. Jule and R. Krishnaraj, *Bioinorg. Chem. Appl.*, 2021, **10**, 1764647.
- 181 J. Yang, L. Yang, M. Fang, L. Li, F. Fu, H. Xu, M. Li and X. Fan, *J. Colloid Interface Sci.*, 2023, **631**, 44–54.
- 182 X. Zhang, J. Chen, S. Jiang, X. Zhang, F. Bi, Y. Yang, Y. Wang and Z. Wang, J. Colloid Interface Sci., 2021, 588, 122–137.
- 183 J. Li, K. Li, B. Lei, M. Ran, Y. Sun, Y. Zhang, K.-H. Kim and F. Dong, *Chem. Eng. J.*, 2021, **413**, 127389.
- 184 M. Zhang, X. Liu, X. Zeng, M. Wang, J. Shen and R. Liu, *Chem. Phys. Lett.*, 2020, **738**, 100049.
- 185 B. N. R. Winayu, W.-H. Mao and H. Chu, Sustainable Environ. Res., 2022, 32, 34.
- 186 V. T. T. Ho, D. H. Chau, K. Q. Bui, N. T. T. Nguyen, T. K. N. Tran, L. G. Bach and S. N. Truong, *Inorganics*, 2022, **10**, 29.
- 187 S. Shajari, E. Kowsari, N. Seifvand, F. Boorboor Ajdari, A. Chinnappan, S. Ramakrishna, G. Saianand, M. Dashti Najafi, V. Haddadi-Asl and S. Abdpour, *Catalysts*, 2021, 11, 126.
- 188 Z. Sun, J. Fan, R. Feng, M. Wang, Y. Zhou and L. Zhang, *J. Chem. Technol. Biotechnol.*, 2021, **96**, 1732–1741.
- 189 Y. Bi, E. Sun, S. Zhang, F. Du, H. Wei, F. Liu and C. Zhao, *Environ. Sci. Pollut. Res.*, 2021, **28**, 57398–57411.
- 190 L. Yang, J. Guo, T. Yang, C. Guo, S. Zhang, S. Luo, W. Dai, B. Li, X. Luo and Y. Li, *J. Hazard. Mater.*, 2021, **402**, 123741.
- 191 P. Mohammadi, F. Ghorbani Shahna, A. Bahrami, A. A. Rafati and M. Farhadian, *Int. J. Environ. Anal. Chem.*, 2022, **102**, 222–242.
- 192 M. Rostami, A. Hassani Joshaghani, H. Mazaheri and A. Shokri, *Int. J. Eng.*, 2021, 34, 756–762.
- 193 X. Zhao, Y. Zhang, M. Wu, W. Szeto, Y. Wang, W. Pan and D. Y. C. Leung, *Appl. Surf. Sci.*, 2020, 527, 146780.
- 194 M. Wu, Y. Zhang, H. Huang and D. Y. C. Leung, *Green Energy Environ.*, 2022, 7, 533–544.
- 195 X. Wang, H. Pan, M. Sun and Y. Zhang, *J. Mater. Chem. A*, 2022, **10**, 6078–6085.

- 196 J. Lyu, L. Zhou, J. Shao, Z. Zhou, J. Gao, Y. Dong, Z. Wang and J. Li, *Chem. Eng. J.*, 2020, 391, 123602.
- 197 J. Liu, P. Wang, W. Qu, H. Li, L. Shi and D. Zhang, *Appl. Catal.*, *B*, 2019, 257, 117880.
- 198 X. Li, Z. Zhu, Q. Zhao and L. Wang, *J. Hazard. Mater.*, 2011, **186**, 2089–2096.
- 199 W. J. Liang, J. Li and Y. Q. Jin, J. Environ. Sci. Health, Part A: Toxic/Hazard. Subst. Environ. Eng., 2010, 45, 1384–1390.
- 200 C. Young, T. M. Lim, K. Chiang and R. Amal, *Water Sci. Technol.*, 2004, **50**, 251–256.
- 201 C. L. Bianchi, S. Gatto, C. Pirola, A. Naldoni, A. Di Michele, G. Cerrato, V. Crocellà and V. Capucci, *Appl. Catal.*, *B*, 2014, 146, 123–130.
- 202 Y. Feng, L. Li, M. Ge, C. Guo, J. Wang and L. Liu, ACS Appl. Mater. Interfaces, 2010, 2, 3134–3140.
- 203 W. M. Shackelford, D. M. Cline, L. Faas and G. Kurth, *Anal. Chim. Acta*, 1983, 146, 15–27.
- 204 R. L. Adkins, in *Kirk-Othmer Encyclopedia of Chemical Technology*, ed. Kirk-Othmer, Wiley, 1st edn, 2000, DOI: 10.1002/0471238961.1409201801041109.a01.pub2.
- 205 D. S. Bhatkhande, S. P. Kamble, S. B. Sawant and V. G. Pangarkar, *Chem. Eng. J.*, 2004, **102**, 283–290.
- 206 D. S. Bhatkhande, V. G. Pangarkar and A. A. Beenackers, *Water Res.*, 2003, **37**, 1223–1230.
- 207 T. Akhtar, H. Nasir, E. Sitara, S. A. B. Bukhari, S. Ullah and R. M. A. Iqbal, *Environ. Sci. Pollut. Res.*, 2022, 29, 49925– 49936.
- 208 D. Li, S. Yu, H. Geng, W. Zhou, D. Mu and S. Liu, *Appl. Surf. Sci.*, 2023, **607**, 154996.
- 209 S. P. Kamble, S. B. Sawant, J. C. Schouten and V. G. Pangarkar, J. Chem. Technol. Biotechnol., 2003, 78, 865–872.
- 210 S. P. Kamble, S. B. Sawant and V. G. Pangarkar, *Ind. Eng. Chem. Res.*, 2003, **42**, 6705–6713.
- 211 R. W. Matthews, M. Abdullah and G.-C. Low, *Anal. Chim. Acta*, 1990, 233, 171–179.
- 212 K. Hofstadler, R. Bauer, S. Novalic and G. Heisler, *Environ. Sci. Technol.*, 1994, **28**, 670–674.
- 213 A. Mills, R. H. Davies and D. Worsley, *Chem. Soc. Rev.*, 1993, 22, 417–425.
- 214 I. Nitoi, P. Oancea, M. Raileanu, M. Crisan, L. Constantin and I. Cristea, *J. Ind. Eng. Chem.*, 2015, 21, 677–682.
- 215 S. Chilukoti, S. Rohit and S. Chikkadasappa, *Ind. Eng. Chem. Res.*, 2015, **54**(32), 7800–7810.
- 216 R. J. Tayade, R. G. Kulkarni and R. V. Jasra, *Ind. Eng. Chem. Res.*, 2006, 45, 922–927.
- 217 A. Ayati, B. Tanhaei, F. F. Bamoharram, A. Ahmadpour, P. Maydannik and M. Sillanpää, *Sep. Purif. Technol.*, 2016, 171, 62–68.
- 218 G. C. J. Swarnavalli, S. Dinakaran, S. Krishnaveni and G. M. Bhalerao, *Mater. Sci. Eng., B*, 2019, **247**, 114376.
- 219 S. S. Boxi and S. Paria, RSC Adv., 2015, 5, 37657-37668.
- 220 L. Zhang, X. He, X. Xu, C. Liu, Y. Duan, L. Hou, Q. Zhou,C. Ma, X. Yang and R. Liu, *Appl. Catal.*, B, 2017, 203, 1–8.
- 221 W. Wang, Y. Huang and S. Yang, in 2010 International Conference on Mechanic Automation and Control Engineering, IEEE, 2010, pp. 1303–1305.

Nanoscale Advances Review

- 222 W.-K. Jo, Y. Won, I. Hwang and R. J. Tayade, Ind. Eng. Chem. Res., 2014, 53, 3455-3461.
- 223 Z. Sun, M. Zhao, F. Li, T. Wang and L. Xu, Mater. Res. Bull., 2014, 60, 524-529.
- 224 S. Zhang, L. Li, Y. Liu and Q. Zhang, Chin. J. Chem. Eng., 2017, 25, 223-231.
- 225 Q. Liu, M. Wen, Y. Guo, S. Song, G. Li and T. An, ACS Appl. Mater. Interfaces, 2022, 14, 55503-55516.
- 226 R. Jevtic, P. A. Ramachandran and M. P. Dudukovic, Ind. Eng. Chem. Res., 2009, 48, 7986-7993.
- 227 S. K. Guha, Y. Obora, D. Ishihara, H. Matsubara, I. Ryu and Y. Ishii, Adv. Synth. Catal., 2008, 350, 1323-1330.
- 228 H. Li, Y. She and T. Wang, Front. Chem. Sci. Eng., 2012, 6, 356-368.
- 229 A. Maldotti, A. Molinari and R. Amadelli, Chem. Rev., 2002, **102**, 3811-3836.
- 230 M. K. Estahbanati, M. Feilizadeh, A. Babin, B. Mei, G. Mul and M. C. Iliuta, Chem. Eng. J., 2020, 382, 122732.
- 231 D. G. Montjoy, E. A. Wilson, H. Hou, J. D. Graves and N. A. Kotov, Nat. Commun., 2023, 14, 857.
- 232 Y. Xiao, J. Liu, J. Mai, C. Pan, X. Cai and Y. Fang, J. Colloid Interface Sci., 2018, 516, 172-181.
- 233 M. A. Brusa and M. A. Grela, J. Phys. Chem. B, 2005, 109, 1914-1918.
- 234 J. J. Murcia, M. C. Hidalgo, J. A. Navío, V. Vaiano, D. Sannino and P. Ciambelli, Catal. Today, 2013, 209, 164-169.
- 235 P. Wen, Y. Zhang, G. Xu, D. Ma, P. Qiu and X. Zhao, J. Mater., 2019, 5, 696-701.
- 236 Y. Shiraishi, Y. Sugano, S. Ichikawa and T. Hirai, Catal. Sci. Technol., 2012, 2, 400-405.
- 237 A. Henríquez, V. Melin, N. Moreno, H. D. Mansilla and D. Contreras, Molecules, 2019, 24, 2244.
- 238 K. Ueyama, T. Hatta, A. Okemoto, K. Taniya, Y. Ichihashi and S. Nishiyama, Res. Chem. Intermed., 2018, 44, 629-638.
- 239 J. T. Carneiro, T. J. Savenije, J. A. Moulijn and G. Mul, J. Photochem. Photobiol., A, 2011, 217, 326-332.
- 240 C. B. Almquist and P. Biswas, Appl. Catal., A, 2001, 214, 259-271.
- 241 H. Einaga, S. Futamura and T. Ibusuki, Appl. Catal., B, 2002, 38, 215-225.
- 242 R. Vinu and G. Madras, Appl. Catal., A, 2009, 366, 130-140.
- 243 V. H. van Dijk, G. Simmelink and G. Mul, Appl. Catal., A, 2014, 470, 63-71.
- 244 P. Du, J. A. Moulijn and G. Mul, J. Catal., 2006, 238, 342-
- 245 E. Fornal and C. Giannotti, J. Photochem. Photobiol., A, 2007, 188, 279-286.
- 246 H. Wang, C. Yu, G. Xu, Y. Zhang, X. Wu and L. Cheng, Mater. Chem. Phys., 2020, 253, 123391.
- 247 K. Shimizu, Y. Murata and A. Satsuma, J. Phys. Chem. C, 2007, 111, 19043-19051.
- 248 Y. Rasouli, M. Abbasi and S. A. Hashemifard, Int. J. Environ. Sci. Technol., 2019, 16, 5595-5610.
- 249 H. Inan, A. Dimoglo, H. Simsek and M. Karpuzcu, Sep. Purif. Technol., 2004, 36, 23-31.

- 250 O. A. Fadali, E. E. Ebrahiem, T. E. Farrag, M. S. Mahmoud and A. El-Gamil, Minia J. Eng. Technol., 2013, 32, 88-101.
- 251 M. A. Tony, P. J. Purcell and Y. Zhao, J. Environ. Sci. Health, Part A: Toxic/Hazard. Subst. Environ. Eng., 2012, 47, 435-440.
- 252 G. H. Ahmed, S. R. M. Kutty and M. H. Isa, Int. J. Appl., 2011, 1, 179-189.
- 253 I. Khouni, G. Louhichi, A. Ghrabi and P. Moulin, Process Saf. Environ. Prot., 2020, 135, 323-341.
- 254 J.-Q. Jiang, Curr. Opin. Chem. Eng., 2015, 8, 36-44.
- 255 R. Asghari, M. S. Safavi and J. Khalil-Allafi, Trans. IMF, 2020, 98, 250-257.
- 256 L. Loredana, G. Ciobanu, S. M. Cimpeanu, O. Kotova, R. Ciocinta, D. Bucur and M. Harja, AgroLife Sci. J., 2019, 8, 139-145.
- 257 W. T. Vieira, M. B. de Farias, M. P. Spaolonzi, M. G. C. da Silva and M. G. A. Vieira, Environ. Chem. Lett., 2020, 18, 1113-1143.
- 258 J. F. Nure and T. T. Nkambule, J. Ind. Eng. Chem., 2023, 126, 92-114.
- 259 J.-S. Seo, Y.-S. Keum and Q. X. Li, Int. J. Environ. Res. Public Health, 2009, 6, 278-309.
- 260 R. Rauhut and G. Klug, FEMS Microbiol. Rev., 1999, 23, 353-370.
- 261 Z. C. Symons and N. C. Bruce, Nat. Prod. Rep., 2006, 23, 845-
- 262 M. Umar and H. A. Aziz, Org. Pollut.: Monit., Risk Treat., 2013, 8, 196-197.
- 263 R. Ameta, S. Benjamin, A. Ameta and S. C. Ameta, in Materials Science Forum, Trans Tech Publ, 2013, vol. 734, pp. 247-272.
- 264 C. S. Turchi and D. F. Ollis, *J. Catal.*, 1990, **122**, 178–192.
- 265 Q. Xiang, J. Yu and P. K. Wong, J. Colloid Interface Sci., 2011, 357, 163-167.
- 266 W. S. Koe, J. W. Lee, W. C. Chong, Y. L. Pang and L. C. Sim, Environ. Sci. Pollut. Res., 2020, 27, 2522-2565.
- 267 R. M. Mohammed and K. M. M. Al-zobai, Solid State Technol., 2020, 63, 5390-5404.
- 268 B. Ogoh-Orch, P. Keating and A. Ivaturi, ACS Omega, 2023, 8, 43556-43572.
- 269 D. A. D. A. Aljuboury and F. Shaik, S. Afr. J. Chem. Eng., 2021, **35**, 69–77.
- 270 Z. Ghasemi, H. Younesi and A. A. Zinatizadeh, J. Taiwan Inst. Chem. Eng., 2016, 65, 357-366.
- 271 F. Shahrezaei, A. Akhbari and A. Rostami, Int. J. Energy Environ., 2012, 3, 267-274.
- 272 E. K. Tetteh, S. Rathilal and D. B. Naidoo, Sci. Rep., 2020, 10, 8850.
- 273 I. Ul Haq, W. Ahmad, I. Ahmad and M. Yaseen, Water Environ. Res., 2020, 92, 2086-2094.
- 274 W. Z. Khan, I. Najeeb, M. Tuiyebayeva and Z. Makhtayeva, Process Saf. Environ. Prot., 2015, 94, 479-486.
- 275 C. P. M. de Oliveira, M. M. Viana and M. C. S. Amaral, J. Water Process Eng., 2020, 34, 101093.
- 276 F. V. Santos, E. B. Azevedo and M. Dezotti, Braz. J. Chem. Eng., 2006, 23, 451-460.
- 277 J. Saien and H. Nejati, J. Hazard. Mater., 2007, 148, 491-495.

278 A. X. R. Corrêa, E. N. Tiepo, C. A. Somensi, R. M. Sperb and C. M. Radetski, *I. Environ. Eng.*, 2010, **136**, 40–45.

- 279 S. A. Malik, Master's thesis, *King Fahd University of Petroleum and Minerals*, Saudi Arabia, 2005.
- 280 P. Stepnowski, E. M. Siedlecka, P. Behrend and B. Jastorff, *Water Res.*, 2002, **36**, 2167–2172.
- 281 J. Saien and F. Shahrezaei, *Int. J. Photoenergy*, 2012, **2012**, 1–5.
- 282 M. D'Auria, L. Emanuele, R. Racioppi and V. Velluzzi, *J. Hazard. Mater.*, 2009, **164**, 32–38.
- 283 E. A. Emam and N. A. K. Aboul-Gheit, *Energy Sources, Part A*, 2014, **36**, 1123–1133.
- 284 E. H. Khader, T. J. Mohammed, T. M. Albayati, N. M. C. Saady and S. Zendehboudi, *J. Mol. Struct.*, 2024, 1304, 137688.
- 285 E. K. Tetteh, B. D. Naidoo and S. Rathilal, *Environ. Eng. Res.*, 2019, **24**, 711–717.
- 286 G. Alhakimi, S. Gebril and L. H. Studnicki, *J. Photochem. Photobiol.*, *A*, 2003, **157**, 103–109.
- 287 C. Kormann, D. W. Bahnemann and M. R. Hoffmann, Environ. Sci. Technol., 1988, 22, 798–806.

- 288 A. Kumar and G. Pandey, *Mater. Sci. Eng. Int. J.*, 2017, 1, 1–10.
- 289 S. Ameen, H.-K. Seo, M. S. Akhtar and H. S. Shin, *Chem. Eng. J.*, 2012, **210**, 220–228.
- 290 J. Zhu, W. Zheng, B. He, J. Zhang and M. Anpo, *J. Mol. Catal. A: Chem.*, 2004, **216**, 35–43.
- 291 C. Adán, J. Carbajo, A. Bahamonde and A. Martínez-Arias, *Catal. Today*, 2009, **143**, 247–252.
- 292 G. Sivalingam, K. Nagaveni, M. S. Hegde and G. Madras, *Appl. Catal.*, *B*, 2003, **45**, 23–38.
- 293 K. Nagaveni, G. Sivalingam, M. S. Hegde and G. Madras, Appl. Catal., B, 2004, 48, 83–93.
- 294 K. Mushtaq, M. Saeed, W. Gul, M. Munir, A. Firdous, T. Yousaf, K. Khan, H. M. R. Sarwar, M. A. Riaz and S. Zahid, *Inorg. Nano-Met. Chem.*, 2020, **50**, 580–586.
- 295 A. Ali, M. Shoeb, Y. Li, B. Li and M. A. Khan, *J. Mol. Liq.*, 2021, **324**, 114696.
- 296 M. Zhou, J. Yu, S. Liu, P. Zhai and B. Huang, *Appl. Catal.*, B, 2009, 89, 160–166.
- 297 F. He, J. Li, T. Li and G. Li, Chem. Eng. J., 2014, 237, 312-321.
- 298 X. Li, G. Chen, Y. Po-Lock and C. Kutal, *J. Chem. Technol. Biotechnol.*, 2003, **78**, 1246–1251.