ChemComm



COMMUNICATION

View Article Online
View Journal | View Issue



Cite this: *Chem. Commun.*, 2020, **56**, 8924

Received 6th May 2020, Accepted 19th June 2020

DOI: 10.1039/d0cc03266b

rsc.li/chemcomm

Synthesis and characterization of low-nuclearity lantern-type porous coordination cages†

Permanent porosity in lantern-type M_4L_4 paddlewheel-based cages is rare and has only been reported for naphthalene, naphthyridine, and diethynylbenzene-based linkers. This work presents the design, synthesis, and characterization of small lanterns that exhibit CO_2 accessible BET surface areas in excess of 200 m² g $^{-1}$. The crystal packing and porosity of these cages can be tuned by either ligand functionalization or the choice of M^{2+} source used in their synthesis. Given their low nuclearity, these cages with internal M-M distances of less than 5 Å represent the lower size limit for permanently microporous coordination cages.

Porous coordination cages have received considerable recent attention, particularly as the number of surface areas reported for them continues to increase.2 The majority of these are higher nuclearity carboxylate-based systems that adopt either tetrahedral,³ octahedral,⁴ or cuboctahedral⁵ structures containing bi-,6 tri-,7 or tetrametallic8 building units.9 Porous paddlewheel-based cages, for example, most commonly adopt M₁₂L₁₂ or M₂₄L₂₄ structures. ¹⁰ In contrast, supramolecular cages based on nitrogen-containing heterocycles, which have been used in catalysis, 11 separations, 12 molecular trapping, 13 and drug delivery,14 have been isolated for a broad range of M:L ratios and overall cage nuclearity from M2L2 through M₄₈L₉₆ and beyond. 15-17 This level of tunability allows for molecular-level control of host-guest interactions. 18 In this regard, there is great need for the development of permanently porous, low-nuclearity cages as their potentially small pore sizes can be tuned for selective binding or activation of small gaseous molecules.19 However, reported porosity in these systems has been rare. 20-22 For these, porous lantern-type cages have been exclusively reported for carboxylate-functionalized

Lah and coworkers described the design and synthesis of a set of Cu₄L₄ lanterns based on functionalized 3,3'-[1,3benzenediyldi-(ethynyl)]dibenzoic acid ligands and showed that groups on the exterior surface of the cage can be used to tune crystal packing and thus gas uptake. 21 This idea has since been elaborated on by numerous researchers in subsequent studies where functionalization of 3,3'-[1,3-benzenediyldi-(ethynyl)]dibenzoic acid was leveraged to tune both inter- and intra-cage space. 22,23 This has resulted in Cu2+ and Rh2+ cages with a variety of tunable catalytic and gas adsorption properties. 24,25,28-32 In terms of the latter, these have included gate-opening effects, tunable adsorption/desorption hysteresis, and most recently, switchable on/off porosity. Zhou and coworkers have shown that the metal-metal spacing on the interior cavity of the cage can be tuned via the utilization of naphthalene-, naphthyridine-, or pyridine-based linkers where the benzoic acid groups are coordinated directly to the central rings (Fig. 1).25 As opposed to the 9-10 Å between metal cations on the interior of the alkyne-based cages, they isolated lanterns with an M-M distance of $\sim 7.5 \text{ Å}$ in their fused-ring system and just 4.8 Å in the pyridine-based cage Mo₄(pdb)₄ (H₂pdb = pyridinedibenzoic acid). They further showed by comparison with a MOF based on lantern-type pores, that the M-M distance in the former is optimal for CO₂ binding.

These larger lantern-type cages based on extended ligands have BET surface areas that span 0 to 485 m 2 g $^{-1}$, and can likely be further increased by utilization of even longer bridging ligands and continued development of the ligand functionalization strategies that were previously reported. However, in terms of the smaller benzene- or pyridine-based cages, surface areas have not been reported. Herein, we discuss the design and synthesis of five novel porous M_4L_4 lantern-type coordination cages based on Cr^{2+} , Cu^{2+} , and Mo^{2+} (Fig. 1). Notably, these

paddlewheel-based building units incorporating either naphthalene, naphthyridine, or diethynylbenzene-type ligands (Fig. 1). Porous M_4L_4 lanterns have been isolated for $\text{Cu}^{2^+},$ $\text{Mo}^{2^+},$ and Rh^{2^+} paddlewheels and ligands with varying levels of functionalization on either their interior or exterior surfaces. $^{23-34}$

^a Department of Chemistry & Biochemistry, University of Delaware, Newark, Delaware 19716, USA. E-mail: edb@udel.edu

b Center for Neutron Science, Department of Chemical and Biomolecular Engineering, University of Delaware, Newark, DE 19716, USA

[†] Electronic supplementary information (ESI) available. CCDC 1998863–1998866. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0cc03266b

Communication ChemComm

Fig. 1 (Top Left) Prominent ligands for porous lantern-type paddlewheel cages that have been combined with Cu, Mo, or Rh to afford M₄L₄ structures. This study focuses on $Cu_4(pdb)_4$, $Cu_4(^tBu-bdb)_4$, and $M_4(tdb)_4$ where M = Cr, Cu, Mo. (Bottom) Structures of $Cu_4(pdb)_4$ (left) and Cu₄(tdb)₄ (right) where green, red, gray, and blue spheres represent copper, oxygen, carbon, and nitrogen atoms, respectively. Although the pyridine-based cage has no C-H on the central ring, the ligand is significantly distorted away from planarity in the crystal structure.

cages lack the alkyne functional groups typically used in the assembly of these systems and represent the lower limit in paddlewheel cage size. The diameter of the pore in these cages is limited by the inter-paddlewheel distance of ~ 5 Å and to the best of our knowledge, are the smallest coordination cages to exhibit permanent porosity.

The syntheses of M₄L₄ lantern-type paddlewheel-based cages proceed similarly to those reported for octahedral or cuboctahedral cages where the solvothermal reaction of metal salts with an organic ligand in amide solvents or amide/alcohol mixtures typically affords cage in high yield. Here, a similar protocol was used for the synthesis of Cu₄(pdb)₄ (H₂pdb = pyridinedibenzoic acid; Fig. 1) For this reaction, 168 mg (1 equiv.) of copper(II) nitrate hemipentahydrate and 207 mg (1 equiv.) of H₂pdb were added to a 20 mL scintillation vial and dissolved in 17 mL N,N-dimethylformamide (DMF). Three mL of methanol

(MeOH) was then layered on top of the solution and the mixture heated to 80 °C in a dry bath overnight. Over the course of the reaction, diffraction-quality single crystals of Cu4(pdb)4 formed in high yield. Structural analysis of this cages reveals it adopts the expected lantern geometry that is nearly identical to the previously reported molybdenum(II) cage, Mo₄(pdb)₄. Both cages crystallize in the same I4/m space group (Table S1, ESI†) with similar cell parameters where a = b = 12.324(1) and c = 24.440(4) Å for $Mo_4(pdb)_4$ and a = b = 12.121(4) and c = 23.730(1) Å for Cu₄(pdb)₄.²³ The decrease in unit cell axes for the latter is largely a result of shorter M-L bond distances (1.96 vs. 2.10 Å) associated with the smaller ionic radius first-row metal. The most dramatic differences in the cages are also a result of the nature of the metal cation, with the d4-based molybdenum cage containing multiplybonded bimetallic clusters with Mo-Mo distances of 2.10 Å while the corresponding Cu-Cu distance (2.587 Å) is significantly longer. As a result of this, the internal metal-metal distance in Cu₄(pdb)₄ is significantly shorter than in Mo₄(pdb)₄ (4.49 Å vs.4.84 Å). The three-dimensional packing of Cu₄(pdb)₄ reveals minimal pore space in the structure. In the a-b plane, each cage interacts with four adjacent cages to form layers that pack in an offset manner along c. The closest intermolecular aromatic ring centroid distances, face-to-face 4.58 Å and face-to-edge 5.89 Å, suggest that pi-pi interactions are not as significant as they are in alkyne extended structures. Instead, the cages pack in a dense conformation where all four bridging ligands occupy the window of an adjacent cage.

Given the moderate porosities previously reported for the extended lantern structures, we targeted solvent exchange and activation procedures to optimize the surface area of Cu₄(pdb)₄. As a result of the close-packed nature of the molecules in the solid state, the cage is completely insoluble and is thus more amenable to solvent exchange protocols commonly used for metal-organic frameworks. Ultimately, a sample was thoroughly washed with fresh DMF over the course of three days and subsequently solvent exchanged with methanol, over the course of which the sample displayed no decrease in crystallinity. A degas survey, wherein a surface area is measured after successive heating steps, indicated the optimal activation temperature for this material was 175 °C. Although Cu₄(pdb)₄ had very little N2 accessible surface area, it had a CO2 accessible BET (Langmuir) surface area of 195 (325) m² g⁻¹. The CO₂ saturation capacity at 195 K and 1.0 bar of 3.55 mmol g^{-1} corresponds to the adsorption of 5 CO₂ molecules/cage.

In order to tune the surface area or solubility of these types of cages, modifications can either be made at the metal cation site or with ligand functionalization. In terms of the latter, the functionalized dibromopyridines that are necessary for this route are significantly more expensive than the analogous benzene-based starting materials. The cages of this type that have been synthesized thus far have largely avoided directlycoupled benzene rings, presumably to avoid the C-H interactions present in these systems. However, close inspection of the crystal structures of Mo₄(pdb)₄ and Cu₄(pdb)₄ indicate that these interactions are avoided given the significant distortion away from planarity in the ligand. Rather than C-H/C-H

ChemComm Communication

interactions driving cage distortion this suggests that the cage structure inherently distorts the ligand. With this in mind, we prepared two functionalized, benzene-based ligands H_2 tdb and H_2 tBu-bdb (Fig. 1). However, these levels of functionalization did not have the desired effect as the former produced cage, $Cu_4(tdb)_4$, that crystallized with nearly identical crystal packing and the latter gave what was presumably cage although we were unable to obtain diffraction quality single crystals. The $Cu_4(tdb)_4$ unit cell has a slightly extended a and b axis of 12.80 Å compared to the $Cu_4(pdb)_4$ cage due to the methyl substituent forcing the cages further apart. It is important to note that in the structure of $Cu_4(tdb)_4$ the C–H groups on the center of the ligand are sufficiently separated as a result of the aforementioned cage-induced ligand distortion (Fig. 1).

To tune cage packing, we instead turned to the synthesis of other metal analogues of M₄(tdb)₄. Similar to the synthesis of the copper cage, both Cr₄(tdb)₄ and Mo₄(tdb)₄ were prepared via solvothermal syntheses, but with care taken to limit their exposure to O₂ given the well-known redox active nature of Mo₂ and Cr₂ paddlewheel units. Crystal structures of M₄(tdb)₄ reveal all three cages adopt the expected geometry and the chromium and copper structures pack the same as M₄(pdb)₄. Cu₄(tdb)₄ and Cr4(tdb)4 have nearly identical unit cells, however the interior paddlewheel-paddlewheel distance of Cu₄(tdb)₄ is 5.04 Å and the Cr₄(tdb)₄ lantern is 5.26 Å, again a result of the shorter M-M distance from the quadruple bond in the latter. The extended structure of Mo₄(tdb)₄ is significantly different than the other cages reported here and the previously reported Mo₄(pdb)₄ phase. This lantern crystallized with two cages in the asymmetric unit, where they sit orthogonal to each other (Fig. 2). An interstitial pore exists between the ligands of the cages with a diameter of 8.76 Å. These toluene-based cages were similarly prepared for gas adsorption measurements by implementing amide and methanol washes. Degas surveys for $M_4(tdb)_4$ gave optimal activation temperatures of 25, 25, and 100 °C for the Cr, Mo, and Cu analogues, respectively.

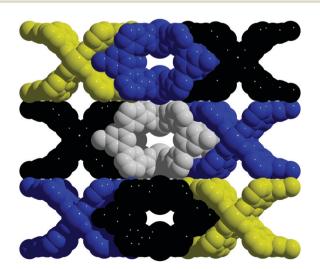


Fig. 2 Solid-state packing of $Mo_4(tdb)_4$ where cages in a given layer alternate by 90 degrees.

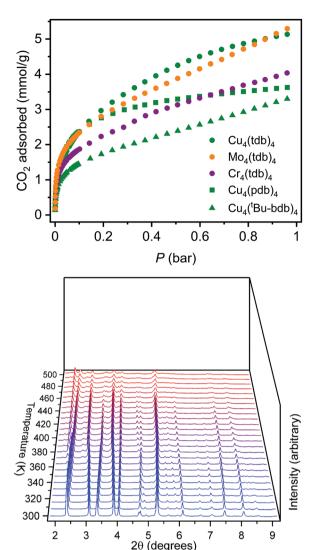


Fig. 3 (Top) CO₂ adsorption in $M_4(L)_4$ cages at 195 K. (Bottom) PXRD patterns as a function of temperature for $Cu_4(tdb)_4$ spanning the temperature range of 300–550 K. During this activation, the cage remains moderately crystalline while undergoing significant structural rearrangement.

These resulted in CO_2 accessible BET (Langmuir) surface areas of 145 (401), 180 (516), and 218 (527) m^2 g^{-1} (Fig. 3). It is notable that CO_2 adsorption isotherms were used to calculate these surface areas, which is more typically done with N_2 adsorption. However, given the small pore sizes of these cages, they were nonporous to N_2 .

As described above, naphthalene bridged lanterns have a M-M distance calculated to be optimal for fitting a single CO₂ molecule in the lantern pore. The crystal structure of these smaller lanterns with M-M distances less than 5.2 Å do not have the interior pore size capable of adsorbing CO₂ in the same manner, although they feature bridging solvent molecules trapped between the metal cation sites. Due to the tight cage packing, accessible pores or channels for gas adsorption are also not expressly visible in the solvated crystal structure. Despite this, these smaller lanterns retain surface areas greater than lanterns extended by fused rings. Solvent exchanging and

Communication ChemComm

activating the lanterns in vacuo likely alter cage packing, potentially allowing gas accessibility. The Cu₄(pdb)₄ and Cu₄(tdb)₄ lanterns are thermally stable with optimal activation temperatures of 175 °C and 100 °C respectively, and remain crystalline upon activation. Methanol exchanged Cu₄(tdb)₄ was characterized with in situ PXRD experiments while under vacuum to monitor crystal structure changes (Fig. 3). As the temperature increases from room temperature to 200 °C, there are clear peak shifts and intensity changes taking place, indicating a transition to a new space group. After heating to 225 °C in vacuo, the material is assumed to be fully activated. Due to preferred orientations in the measured sample, a satisfactory space group could not be obtained, however new unit cell dimensions could be acquired via Pawley refinement. Fitting the diffraction pattern collected at 225 °C yielded a distinctly different unit cell with a = 21.91 Å, b = 16.83 Å, and c = 22.06 Å (from a = b = 12.859 Å, and c = 23.956 Å). Removal of solvent, cage rearrangement, and defects in the structure disrupt the periodicity of the sample, resulting in much larger unit cell dimensions. It is likely that as these structure changes take place, accessible pore spaces become available which explains the surprisingly high surface areas for coordination cages of this size.

The foregoing results demonstrate the importance of both ligand functionalization and metal cation selection in the synthesis of small, porous lantern-type coordination cages. These reported structures represent the smallest versions of these cages that can be synthesized and yet they display BET surface areas as high as 200 m² g⁻¹. It is expected that further functionalization on the backbone of this ligand scaffold can be leveraged to tune the extra-pore space in the structure and tune solubility and stability of porous lanterns. Work in our lab along these lines will focus on the utilization of ester- and amide-functionalization routes.

Crystal structures were submitted to the Cambridge Structural Database under the CCDC numbers 1998863-1998866.† This material is based upon work supported by the U.S. Department of Energy's Office of Energy Efficiency and Renewable Energy under the Hydrogen and Fuel Cell Technologies and Vehicle Technologies Offices under Award Number DE-EE0008813. This research used resources of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

Conflicts of interest

There are no conflicts to declare.

References

1 N. Ahmad, A. H. Chughtai, H. A. Younus and F. Verpoort, Coord. Chem. Rev., 2014, 280, 1-27.

- 2 X. X. Li, D. Zhao and S. T. Zheng, Coord. Chem. Rev., 2019, 397, 220-240.
- 3 A. C. Sudik, A. R. Millward, N. W. Ockwig, A. P. Côté, J. Kim and O. M. Yaghi, J. Am. Chem. Soc., 2005, 127, 7110-7118.
- 4 C. A. Rowland, G. R. Lorzing, E. J. Gosselin, B. A. Trump, G. P. A. Yap, C. M. Brown and E. D. Bloch, J. Am. Chem. Soc., 2018, 140, 11153-11157
- 5 M. Eddaoudi, J. Kim, J. B. Wachter, H. K. Chae, M. O'Keeffe and O. M. Yaghi, J. Am. Chem. Soc., 2001, 123, 4368-4369.
- 6 Y. Peng, V. Krungleviciute, I. Eryazici, J. T. Hupp, O. K. Farha and T. Yildirim, J. Am. Chem. Soc., 2013, 135, 11887-11894.
- 7 G. Liu, Y. Di Yuan, J. Wang, Y. Cheng, S. B. Peh, Y. Wang, Y. Qian, J. Dong, D. Yuan and D. Zhao, J. Am. Chem. Soc., 2018, 140, 6231-6234.
- 8 N. L. Rosi, J. Eckert, M. Eddaoudi, D. T. Vodak, J. Kim, M. O'Keeffe and O. M. Yaghi, Science, 2003, 300, 1127-1129.
- 9 D. J. Tranchemontagne, Z. Ni, M. O'Keeffe and O. M. Yaghi, Angew. Chem., Int. Ed., 2008, 47, 5136-5147.
- 10 G. R. Lorzing, B. A. Trump, C. M. Brown and E. D. Bloch, Chem. Mater., 2017, 29, 8583-8587.
- 11 M. Pan, K. Wu, J. H. Zhang and C. Y. Su, Coord. Chem. Rev., 2019, 378, 333-349,
- 12 B. Li, T. He, Y. Fan, X. Yuan, H. Qiu and S. Yin, Chem. Commun., 2019, 55, 8036-8059,
- 13 S. Horiuchi, T. Murase and M. Fujita, J. Am. Chem. Soc., 2011, 133, 12445-12447.
- 14 B. Woods, M. N. Wenzel, T. Williams, S. R. Thomas, R. L. Jenkins and A. Casini, Front. Chem., 2019, 7, 1-6.
- 15 L. M. Mesquita, J. Anhäuser, D. Bellaire, S. Becker, A. Lützen and
- S. Kubik, Org. Lett., 2019, 21, 6442-6446. 16 D. Fujita, Y. Ueda, S. Sato, N. Mizuno, T. Kumasaka and M. Fujita, Nature, 2016, 540, 563-566.
- 17 R. Chakrabarty, P. S. Mukherjee and P. J. Stang, Chem. Rev., 2011, 111, 6810-6918.
- 18 M. D. Pluth and K. N. Raymond, Chem. Soc. Rev., 2007, 36,
- 161-171. 19 D. Preston, K. F. White, J. E. M. Lewis, R. A. S. Vasdev, B. F. Abrahams and J. D. Crowley, Chem. - Eur. J., 2017, 23, 10559-10567.
- 20 F. A. Cotton, L. M. Daniels, C. Lin and C. A. Murillo, Chem. Commun., 1999, 841-842.
- 21 G. R. Lorzing, E. J. Gosselin, B. S. Lindner, R. Bhattacharjee, G. P. A. Yap, S. Caratzoulas and E. D. Bloch, Chem. Commun., 2019, 55, 9527-9530.
- 22 P. W. V. Butler, P. E. Kruger and J. S. Ward, Chem. Commun., 2019, 55, 10304-10307.
- 23 M. J. Prakash, M. Oh, X. Liu, K. N. Han, G. H. Seong and M. S. Lah, Chem. Commun., 2010, 46, 2049-2051.
- 24 J.-R. Li and H.-C. Zhou, Nat. Chem., 2010, 2, 893-898.
- 25 J.-R. Li, A. A. Yakovenko, W. Lu, D. J. Timmons, W. Zhuang, D. Yuan and H.-C. Zhou, J. Am. Chem. Soc., 2010, 132, 17599-17610.
- 26 W. Lu, D. Yuan, A. Yakovenko and H.-C. Zhou, Chem. Commun., 2011, 47, 4968-4970.
- 27 J.-R. Li, J. Yu, W. Lu, L.-B. Sun, J. Sculley, P. B. Balbuena and H.-C. Zhou, Nat. Commun., 2013, 4, 1538.
- 28 V. Brega, M. Zeller, Y. He, H. P. Lu and J. K. Klosterman, Chem. Commun., 2015, 51, 5077-5080.
- 29 L. Chen, J. Kang, H. Cui, Y. Wang, L. Liu, L. Zhang and C.-Y. Su, Dalton Trans., 2015, 44, 12180.
- 30 L. Chen, T. Yang, H. Cui, T. Cai, L. Zhang and C.-Y. Su, J. Mater. Chem. A, 2015, 3, 20201.
- 31 S. A. Boer and D. R. Turner, Chem. Commun., 2015, 51, 17375–17378.
- 32 G. A. Craig, P. Larpent, S. Kusaka, R. Matsuda, S. Kitagawa and S. Furukawa, Chem. Sci., 2018, 9, 6463-6469.
- 33 G. A. Craig, P. Larpent, H. Urabe, A. Legrand, M. Bonneau, S. Kusaka and S. Furukawa, Chem. Commun., 2020, 56, 3689-3692.
- W. M. Bloch, R. Babarao and M. L. Schneider, Chem. Sci., 2020, 11, 3664-3671.