


Cite this: *RSC Adv.*, 2022, 12, 30056

# Current state of copper-based bimetallic materials for electrochemical CO<sub>2</sub> reduction: a review

Otmane Zoubir,<sup>a</sup> Lahoucine Atourki,<sup>a</sup> Hassan Ait Ahsaine<sup>\*b</sup> and Amal BaQais<sup>c</sup>

The increasing CO<sub>2</sub> concentration in the atmosphere has caused profound environmental issues such as global warming. The use of CO<sub>2</sub> as a feedstock to replace traditional fossil sources holds great promise to reduce CO<sub>2</sub> emissions. The electrochemical conversion of CO<sub>2</sub> has attracted much attention because it can be powered by renewable sources such as solar energy. In this review article, we provide insight into the important parameters when studying CO<sub>2</sub>RR and give a comprehensive review on the description of synthesis methods with electrocatalytic CO<sub>2</sub> reduction over bimetallic copper-based materials. Due to the important bibliographic data on Cu bimetallic materials, we have limited this review to Sn, In, Pd, Zn and Ag. At the end of this review, challenges and perspectives for further upgrading have been included to briefly highlight the important future considerations of this rapidly growing technology.

Received 27th August 2022  
Accepted 13th October 2022

DOI: 10.1039/d2ra05385c

rsc.li/rsc-advances

## 1. Introduction

The intensification of human industrial activities has gradually disrupted environmental stability on earth, causing more CO<sub>2</sub> production.<sup>1</sup> The increasing CO<sub>2</sub> concentration level in the atmosphere has resulted in severe problems such as the greenhouse effect, leading to global warming, melting glaciers, and more disastrous weather.<sup>2</sup> Therefore, it is of critical importance to reduce atmospheric CO<sub>2</sub> concentration. To this end, much effort has been devoted to define potential methods to mitigate CO<sub>2</sub> emissions. An appealing solution is to use CO<sub>2</sub> as the carbon source to produce value-added products such as carbon monoxide (CO), formic acid (HCOOH), formate (HCOO<sup>-</sup>), methanol (CH<sub>3</sub>OH), methane (CH<sub>4</sub>), ethylene (C<sub>2</sub>H<sub>4</sub>), ethanol (C<sub>2</sub>H<sub>5</sub>OH), as well as others by applying the renewable energy as energy input.<sup>3</sup> A variety of alternative CO<sub>2</sub> utilization approaches are being studied, including biological,<sup>4</sup> thermochemical,<sup>5,6</sup> photochemical<sup>7–10</sup> and electrochemical methods.<sup>11–14</sup> For thermochemical CO<sub>2</sub> conversion *via* a reforming process, it requires not only high reaction temperatures and pressures but also an equal amount of hydrogen as the reducing agent, which is energetically hazardous for large-scale applications. For the photochemical process, the selectivity and production rate of the photocatalytic active systems are too low to be economically valid. In contrast,

CO<sub>2</sub> electrochemical reduction (CO<sub>2</sub>RR) appears to be one of the most promising technologies owing to its feasible operating conditions, scalability, and the increasing sources of green electricity with zero-CO<sub>2</sub> emissions.<sup>15</sup> However, challenges still exist such as slow electron transfer kinetics resulting in low exchange current densities, low energetic efficiency, and poor selectivity.<sup>16</sup>

The development of efficient electrocatalysts plays a key role in the electrochemical reduction of CO<sub>2</sub> in terms of activity and selectivity.<sup>17</sup> Over the last few decades, enormous efforts have been devoted into investigating CO<sub>2</sub> electrocatalysts for the electrochemical CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR).<sup>2</sup> The most commonly explored electrocatalysts for CO<sub>2</sub> reduction can be divided into three groups: metallic; non-metallic; molecular catalysts. Polycrystalline monometallic catalysts offer unique merits such as simple structure, ease of handling, robustness, and other advantages, making them particularly appealing candidates for fundamental research.<sup>14</sup> Based on the primary CO<sub>2</sub> reduction product, four distinct groups of monometallic catalysts have been identified: (1) CO selective metals such as (Pd, Au, Zn, Ag, and Ga); (2) metals that mainly produce HCOOH (*e.g.*, Hg, Pb, Cd, In, Sn, and Ti); (3) metals that form hydrocarbons such as CH<sub>4</sub> and C<sub>2</sub>H<sub>4</sub> (*e.g.*, Cu); (4) metals that mainly produce hydrogen, H<sub>2</sub> (Ni, Pt, Fe, and Ti). Among all the aforementioned monometallic CO<sub>2</sub> electrocatalysts, copper (Cu) is the only metal that can deeply reduce CO<sub>2</sub> to products such as hydrocarbons and alcohols with acceptable activity and efficiency.<sup>18</sup> However, the selectivity of Cu toward certain products is typically poor.<sup>19</sup> Recently, there has been growing interest in bimetallic catalysts for CO<sub>2</sub> reduction; they represent new trends and opportunities in electrochemical CO<sub>2</sub>

<sup>a</sup>MANAPSE Lab, Faculty of Sciences, Mohammed V University in Rabat, Morocco. E-mail: latourki@um5r.ac.ma

<sup>b</sup>Laboratoire de Chimie Appliquée des Matériaux, Faculty of Sciences, Mohammed V University in Rabat, Morocco. E-mail: h.aitahsaine@um5r.ac.ma

<sup>c</sup>Department of Chemistry, College of Science, Princess Nourah bint Abdulrahman University, P.O. Box 84428, Riyadh 11671, Saudi Arabia



conversion.<sup>20,21</sup> Metals and metal oxide-based catalysts especially the Cu based electrocatalysts have been substantially reported as efficient CO<sub>2</sub>RR catalysts.<sup>22–24</sup>

They are easy to synthesize, relatively stable in working conditions. These materials do not require special preparation conditions compared to other molecular. Many remarkable contributions that have been reported using serious preparation control of structures in morphological tailoring,<sup>25</sup> steering surfaces,<sup>23</sup> Metal atom decoration,<sup>26</sup> atomic scale structuration,<sup>27</sup> guided alloying,<sup>28,29</sup> electrolyte design,<sup>30</sup> and strained surfaces.<sup>31</sup> As robust as Cu based electrodes are, they still suffer from a reconstruction during electrolysis. This double-edged sword can degrade the efficiency of the catalysts with altering the well-defined Cu morphology and highly active sites,<sup>32,33</sup> or reconstructs the generating unique Cu active sites with increased catalytic activity for specific products.<sup>34</sup>

The focus throughout this article will be on the use of copper-based bimetallic materials to reduce carbon dioxide into value-added products. We have reviewed the Cu-M electrocatalysts (M: Sn, In, Pd, Zn and Ag) as they the most important reported electrocatalysts for CO<sub>2</sub>RR in the last decade. In this article, we will start by discussing the basic principles of CO<sub>2</sub> electroreduction, including thermodynamics, reaction mechanism, and factors influencing CO<sub>2</sub> electroreduction. Next, we will look at the electrochemical methods for CO<sub>2</sub> electroreduction. Finally, copper-based bimetallic materials will be discussed in detail, including synthesis approaches and catalytic performance.

## 2. Fundamentals of electrocatalytic CO<sub>2</sub> reduction

### 2.1 Thermodynamics of CO<sub>2</sub> reduction

In thermodynamic, the Gibbs free energy ( $G$ ) can be used to determine the maximum amount of reversible work that can be derived from any system at constant pressure ( $P$ ) and temperature ( $T$ ). The change in Gibbs energy  $\Delta G$  can be used to measure the spontaneity of a specific reaction. If the Gibbs free energy decreases while the reaction proceeds, the reactants will spontaneously be converted into products. If  $G$  increases, the reaction will spontaneously proceed in the opposite direction, thereby making the starting materials.<sup>35</sup>

In electrochemistry, Gibbs energy can be accurately controlled by applied potential as shown in equation (Qiao *et al.* 2016):<sup>36</sup>

$$\Delta G = -nFE_{\text{cell}} \quad (1)$$

where  $n$  represents the number of electrons transferred during the electrochemical process,  $E_{\text{cell}}$  is the cell potential, and  $F$  is Faraday's constant.

This equation indicates the quantitative relationship between chemical energy and electrical energy in cell reactions (Table 1).

### 2.2 Reaction mechanism

Researchers across the world have devoted tremendous effort to understand the mechanism for CO<sub>2</sub> electrochemical reduction.

Table 1 Standard Gibbs energies of formation at 298 K, 1 atm (ref. 37)

Product	Gibbs free energy $\Delta G$ (kJ mol <sup>-1</sup> )
C	0
CO	-137.3
CO <sub>2</sub>	-394.4
CH <sub>4</sub>	-50.8
C <sub>2</sub> H <sub>4</sub>	-68.1
CH <sub>3</sub> OH	-161.6
H <sub>2</sub> O (steam)	-228.6
H <sub>2</sub> O (water)	-237.2
O <sub>2</sub>	0
H <sub>2</sub>	0

Especially, why different metals generate different products. In this regard, they have proposed many pathways for electrochemical reduction (ERC), and continue to propose novel reaction pathways based on their understanding of CO<sub>2</sub> reduction on metallic electrodes. However, since ERC is a surface phenomenon, there is no generalized reaction towards the products obtained. The mechanism must depend on the type and morphology of the catalyst.<sup>38,39</sup> The electrochemical reduction of CO<sub>2</sub> is a multi-step reaction process that may proceed *via* two to fourteen electron reaction pathways (Table 2) and yielding diverse reduction products. This multi-step reaction generally involves three major steps: (1) chemical adsorption of CO<sub>2</sub> on the surface of the catalyst; (2) electron/proton transfer to separate C–O bonds and/or form C–H bonds; (3) desorption of products from the surface of electrocatalyst and diffusion into the electrolyte.<sup>40</sup>

In a typical CO<sub>2</sub> electrolyzer, anode and cathode are placed into two chambers separated with an ion-conducting membrane. At the anode, water is oxidized to form molecular oxygen, while CO<sub>2</sub> is reduced to form carbon species at the cathode. The thermodynamic potential that allows the one-electron reduction of CO<sub>2</sub> to form CO<sub>2</sub><sup>-</sup> is -1.90 V vs. SHE in pH 7.0 aqueous solution, making the reaction uphill and unfavorable.<sup>41–43</sup> The first step involves one-electron transfer to generate a key intermediate CO<sub>2</sub><sup>-</sup>, which is the rate-limiting step in the reaction. In contrast, proton-assisted multi-electron transfer processes are more advantageous and take place almost

Table 2 Standard electrochemical potentials for CO<sub>2</sub> reduction<sup>16,54</sup>

Product	Reduction potentials of CO <sub>2</sub>	$E^\circ$ (V) vs. SHE (pH 7)
Carbon monoxide	CO <sub>2</sub> + 2e <sup>-</sup> + 2H <sup>+</sup> → CO(g) + H <sub>2</sub> O	-0.53
Hydrogen	2e <sup>-</sup> + 2H <sup>+</sup> → H <sub>2</sub> (g)	-0.42
Formic acid	CO <sub>2</sub> + 2e <sup>-</sup> + 2H <sup>+</sup> → HCOOH(l) + H <sub>2</sub> O	-0.61
Formaldehyde	CO <sub>2</sub> + 4e <sup>-</sup> + 4H <sup>+</sup> → CH <sub>2</sub> O(l) + H <sub>2</sub> O	-0.50
Methanol	CO <sub>2</sub> + 6e <sup>-</sup> + 6H <sup>+</sup> → CH <sub>3</sub> OH(l) + H <sub>2</sub> O	-0.39
Methane	CO <sub>2</sub> + 8e <sup>-</sup> + 8H <sup>+</sup> → CH <sub>4</sub> (g) + H <sub>2</sub> O	-0.25
Ethylene	CO <sub>2</sub> + 12e <sup>-</sup> + 12H <sup>+</sup> → C <sub>2</sub> H <sub>4</sub> (g) + 4H <sub>2</sub> O	-0.38
Ethane	CO <sub>2</sub> + 14e <sup>-</sup> + 14H <sup>+</sup> → C <sub>2</sub> H <sub>6</sub> (g) + 4H <sub>2</sub> O	-0.28





© 2022 The Author(s). Published by the Royal Society of Chemistry



Fig. 2 (Up): (a) Faradaic efficiencies, (b) current densities for electrochemical CO<sub>2</sub> reduction at a Sn/Cu-PVDF GDE at (−0.6 to −1.2 V vs. RHE). (Bottom): (a) Scheme and (b) cross-sectional SEM image of a Sn/Cu-PVDF/AEM assembly used for electrocatalytic reduction of gaseous CO<sub>2</sub>. Reproduced with permission.<sup>66</sup> Copyright ©2019, Wiley-VCH.

### 3.1 Cu–Sn bimetallic materials

Wang *et al.*<sup>65</sup> have reported the unexplored phase and structural engineering of Cu/Sn catalysts for enhancing CO<sub>2</sub> reduction reaction by simple thermal annealing of CuSn core-shell NPs in controlled conditions. Cu–SnO<sub>2</sub> catalysts were engineered with three distinct structures: the CuO/hollow SnO<sub>2</sub> heterostructure of CuSn NPs/C-A, the Cu<sub>41</sub>Sn<sub>11</sub>@SnO<sub>2</sub> core-shell structure of CuSn NPs/C-H and the Cu NPs/hollow SnO<sub>2</sub> Janus structure of CuSn NPs/C-AH. The electrocatalytic performance results showed that CO was the main product of the CO<sub>2</sub> reduction reaction under the potential of −0.7 V vs. RHE. The CuSn NPs/C-A catalyst achieved (70.1% FE<sub>CO</sub>) and CuSn NPs/C-AH (45.1% FE<sub>CO</sub>), which outperformed CuSn NPs/C-H (20.1% FE<sub>CO</sub>), Cu NPs/C (13.5% FE<sub>CO</sub>), and SnO<sub>2</sub> NSL/C (8.4% FE<sub>CO</sub>). Furthermore, at the same potential (−0.7 V vs. RHE) the CuSn NPs/C-A exhibited the highest current density of CO approximately (1.66

mA cm<sup>−2</sup>), which surpassed the CuSn NPs/C-AH (0.86 mA cm<sup>−2</sup>) and Cu NPs/C (0.28 mA cm<sup>−2</sup>) and was far better than the CuSn NPs/C-H (0.21 mA cm<sup>−2</sup>) and SnO<sub>2</sub> NSL/C (0.05 mA cm<sup>−2</sup>). It is clear that there was a selectivity transformation from CO to HCOOH when the electrolysis potential is changed from −0.7 V vs. RHE to −1.0 V vs. RHE. For all catalysts except Cu NPs/C, the main product of CO<sub>2</sub> reduction reaction was HCOOH. By contrast, CuSn NPs/C-A still exhibited the highest FE<sub>HCOOH</sub> of 71.5%. Moreover, at −1.0 V vs. RHE, CuSn NPs/C-A reached the maximum partial current density of HCOOH around (12.6 mA cm<sup>−2</sup>), which was higher than the values of the CuSn NPs/C-AH (10.5 mA cm<sup>−2</sup>), Cu NPs/C, and SnO<sub>2</sub> NSL/C. In addition, the investigation of the stability using chronoamperometry at −0.7 V vs. RHE indicated that CuSn NPs/C-A, CuSn NPs/C-AH, CuSn NPs/C-H catalyst exhibited stable current densities in the span of 10 h. Ju *et al.*<sup>66</sup> demonstrated the importance of using CO<sub>2</sub> gaseous as a feedstock to enhance CO<sub>2</sub>





Fig. 3 (a) Faradaic efficiencies for HCOO<sup>-</sup> at potential range from -0.75 V to -1.15 V vs. RHE. (b) CO and H<sub>2</sub> faradaic efficiencies on the polished Cu, M Sn, BM Sn-Cu at potential range from -0.75 V to -1.15 V vs. RHE in saturated 0.1 M KHCO<sub>3</sub>. (c) The partial current density of HCOO<sup>-</sup> on the polished Cu, M Sn, BM Sn-Cu, M Sn, BM Sn-Cu. (d) Proposed reaction mechanism for CO<sub>2</sub> electrochemical reduction to HCOO<sup>-</sup> of BM Sn-Cu electrode. Reproduced with permission.<sup>67</sup> Copyright ©2019, Elsevier.

mass transport and achieve high CO partial current density. In this regard, the authors employed Sn/Cu-nanofiber electrodes as freestanding gas diffusing electrodes GDEs. They fabricated electrospun polyvinylidene fluoride (PVDF) nanofibers with uniform Cu coating and then used electrochemical under-potential deposition (UPD) to decorate the surface of Cu with Sn. The faradaic efficiencies for CO (Fig. 2) were above 80% at potential  $\leq -0.9$  V and the partial current densities for CO exhibited 104 mA cm<sup>-2</sup> at -1.2 V. However, at potentials  $\leq -1.0$  V a sparse amount of C<sub>2</sub>H<sub>4</sub> less than 8.2% has been detected with current densities lower than 10 mA cm<sup>-2</sup> (Fig. 2).

Furthermore, the Sn/Cu-PVDF GDE maintained long-term stability of 135 h at -1.0 V with the average CO FE (84.9%), while the average FEs for H<sub>2</sub> and C<sub>2</sub>H<sub>4</sub> were 10.6% and 4.4%, respectively. In addition, it has been shown that the relatively high permeability of Sn/Cu nanofiber GDEs was essential for ensuring high CO<sub>2</sub> to CO conversion rates and inhibiting the hydrogen evolution reaction. Jiang *et al.*<sup>67</sup> provided a method for producing a high-performance bimetallic catalyst using an electronically regulated Cu in a heterogeneous bimetallic catalyst of Sn nanoparticles. The performance of the BM Sn-Cu catalyst was investigated under a wide potential range (from -0.75 V to -1.15 V vs. RHE). The BM Sn-Cu catalyst generated HCOO<sup>-</sup> as the primary product during CO<sub>2</sub> electrochemical reduction. As shown in (Fig. 3a) the BM Sn-Cu electrode

demonstrated the higher faradaic efficiency toward HCOO<sup>-</sup> about 92% at -0.95 V vs. RHE, while the total faradaic efficiency of CO and H<sub>2</sub> on the BM Sn-Cu electrode was less than 10% (Fig. 3b). The authors suggested that Sn plays a key in the enhanced catalytic performance of BM Sn-Cu catalyst toward HCOO<sup>-</sup>. The electrocatalytic activity of Cu polished, BM Sn-Cu, and M Sn electrodes was examined under potentiostatic conditions in potential ranges from 0 to -1.2 V vs. RHE. The current density measurements (Fig. 3c) showed that among all electrodes, BM Sn-Cu electrode exhibited a higher HCOO<sup>-</sup> partial current density of 10.8 mA cm<sup>-2</sup> at -0.95 V vs. RHE. This finding confirms that the embedded structure of BM Sn-Cu electrode can provide more active sites for CO<sub>2</sub> reduction. The DFT calculations were performed to understand the electronic structure of BM Sn-Cu catalyst for CO<sub>2</sub> electrochemical reduction. It was found that regulating the electronic structure of the catalyst promotes the formation of the HCOO\* intermediate. Fig. 3d illustrates the proposed mechanism reaction for CO<sub>2</sub> electrochemical reduction to HCOO<sup>-</sup> on the BM Sn-Cu electrode.

Ye *et al.*<sup>68</sup> developed a new approach for designing the Cu-Sn alloy catalyst toward the electroreduction of CO<sub>2</sub> to HCOO<sup>-</sup> through a modified electrodeposition method. For the electrocatalytic performances, the Cu-Sn catalyst was evaluated under a wide potential range (from -0.7 V to -1.2 V vs. RHE). The Cu-





Fig. 4 (a) Effect of applied potential on product distribution and current density of c/s Cu Sn NW@foam for CO<sub>2</sub>RR. (b) Stability of c/s Cu Sn NW@foam catalyst for CO<sub>2</sub>RR by re-repeated use. Reproduced with permission.<sup>70</sup> Copyright ©2018, Wiley-VCH.

Sn catalyst produced HCOO<sup>-</sup> as the main product during CO<sub>2</sub> electrochemical reduction. The catalyst reduced the faradaic efficiency for H<sub>2</sub> evolution from (>90% at -0.75 V vs. RHE) to (less than 10% at -1.14 V vs. RHE) and improved the HCOO<sup>-</sup> faradaic efficiency reaching 82.3% at -1.14 V vs. RHE. In contrast, Sn on CFC catalyst exhibited HCOO<sup>-</sup> faradaic efficiency of greater than 55% at -1.14 V vs. RHE while few amounts of H<sub>2</sub> and CO were also obtained. The authors attributed the improved performance of Sn-Cu alloy catalyst towards HCOO<sup>-</sup> production to the stepped (211) surface of the Cu-Sn alloy. The HCOO<sup>-</sup> mass activity of Cu-Sn alloy catalyst increased along with increasing the applied potential reaching the maximum (1490.6 mA mg<sup>-1</sup>) at -1.14 V vs. RHE. However, the HCOO<sup>-</sup> mass activity of the Cu-Sn catalyst decreased with the increase of the deposition time. The result showed that the highest mass activity was achieved at a deposition time of 0.01 s. Moreover, the authors investigated the correlation between CO<sub>2</sub>RR performance and Sn deposition time. To this end, the results demonstrated that the faradaic efficiency of HCOO<sup>-</sup> remained stable at higher than 82% under various electrodeposition times. Dong *et al.*<sup>69</sup> demonstrated the effect of the local corrosion phenomenon of Cu-Sn catalysts on the catalytic selectivity of CO<sub>2</sub> reduction *via* the patterning of the Sn layer on Cu foil. They found that the thickness of Sn patterns has a significant impact on the surface composition of Cu and Sn. In the Cu-Sn catalyst preparation, the Cu foil was electrochemically polished in the H<sub>3</sub>PO<sub>4</sub> solution for 180 s by applying an anodic potential of 2.5 V *versus* the IrO<sub>x</sub> counter electrode. Then, the Cu foil was cleaned with deionized water and dried using N<sub>2</sub> blowing.

For the photolithography process, the photoresist was spin-coated for 40 s at 6000 rpm and softly baked for 60 s at 110 °C. The photoresist-coated sample was moved to a mask aligner, and then the samples were contacted with a patterned photo-mask. The prepared Cu-Sn catalyst was sealed with epoxy except for the active area of the electrode (0.283 cm<sup>2</sup>). In order to investigate catalytic performances, the authors prepared four samples denoted as Cu foil, Cu/Sn 3 nm, Cu/p-Sn 3 nm, and Cu/p-Sn 20 nm and they evaluated them at different applied potentials from -0.6 V to -1.2 V vs. RHE. The Cu foil obtained

a faradaic efficiency of greater than 50% at all potentials and began to produce CH<sub>4</sub> at high potentials (-1.2 V<sub>RHE</sub>). In contrast, constructing a thick Sn layer 3 nm on Cu foil suppressed the H<sub>2</sub> evolution (FE<sub>H<sub>2</sub></sub> < 5.5%) and increased the selectivity towards HCOOH (FE<sub>HCOOH</sub> > 80%) at high potentials (from -0.8 V<sub>RHE</sub> to -1.2 V<sub>RHE</sub>). The Cu/p-Sn 3 nm exhibited unique selectivity towards CO, the faradaic efficiency reached the highest value (FE<sub>CO</sub> = 58.1%) at -1.0 V vs. RHE. At a potential of -1.2 V<sub>RHE</sub> the FE<sub>CO</sub> of Cu/p-Sn catalyst decreased and FE<sub>CH<sub>4</sub></sub> increased. On the other hand, Cu/p-Sn (20 nm) showed an increased selectivity towards HCOOH about 61.6% at -1.2 V<sub>RHE</sub>. Furthermore, the authors investigated the effect of the patterning of Sn (*t*<sub>Sn</sub>) on the catalytic selectivity of bimetallic Cu-Sn catalyst. They measured the faradaic efficiencies of Cu/Sn and Cu/p-Sn for various *t*<sub>Sn</sub> values. The Cu/Sn catalyst with a thin Sn layer (*t*<sub>Sn</sub> = 1 nm) exhibited a high CO FE of 86.1% at -1.0 V<sub>RHE</sub>. However, the Cu/Sn catalyst with (*t*<sub>Sn</sub> > 2 nm) showed a high FE<sub>HCOOH</sub> of greater than 80% at -1.0 V<sub>RHE</sub>. In comparison to Cu/Sn, the Cu/p-Sn catalyst with thin Sn patterns (between 2 nm to 4 nm) exhibited a high FE<sub>CO</sub> of greater than 51.2%. However, increasing Sn patterns (*t*<sub>Sn</sub> > 5 nm) resulted in a decrease in CO FE (40%) and an increased in HCOOH FE to 59.7%. Hu *et al.*<sup>70</sup> synthesized Cu-Sn core-shell nanowire array catalysts based on 3-D macroporous nickel (Ni) foams through two-step deposition annealing and electroreduction treatment. The electrochemical characterizations for CO<sub>2</sub>RR revealed that constructing a Sn shell on Cu nanowires reduced faradaic efficiencies for H<sub>2</sub> from 55.7% to 10.1% and HCOOH formation from 12.3% to 2% and improved CO faradaic efficiency reaching 90% instead of 32% at an applied potential of -0.8 V vs. RHE. The authors attributed the improved performance to the suppressed adsorption of H\* and the ordered arrangement of Sn and Cu atoms. Moreover, the authors investigated the correlation between CO<sub>2</sub>RR performance and Sn deposition time. The results showed that the efficiency of CO increased with increasing the deposition time reaching the maximum at 10 s and then decreased with time while HCOOH, H<sub>2</sub> efficiencies are on an opposite trend. Furthermore, the effect of applied potential of c/s Cu-Sn NW foam was also investigated, indicating that the production selectivity toward CO remained



stable between  $-0.6$  to  $-1.2$  V with a faradaic efficiency higher than 90% and, the total current density reached  $-13.2$  and  $-19.3$  mA cm $^{-2}$  between  $-0.8$  to  $-1.2$  V vs. RHE. In terms of stability, the Cu–Sn core/shell nanowire array catalyst exhibited good stability. After 8 cycles of use, the catalyst achieved stable current densities of 2 h for each cycle (Fig. 4). According to the authors, good stability could be ascribed to the formation of Cu $_6$ Sn $_5$  in the interface.

Sarfraz *et al.*<sup>71</sup> prepared a highly CO selective catalyst by the electrodeposition of Sn on the surface of oxide-derived copper (OD-Cu). To elucidate the catalytic performance the authors prepared three samples: Sn deposited on OD-Cu denoted as (Cu–Sn), OD-Cu, and Sn deposited on Sn. The CO $_2$ RR electrocatalytic showed that Cu–Sn exhibited a CO faradaic efficiency of greater than 90% over a wide potential range (from  $-0.5$  to

$-0.8$  V vs. RHE), while only trace of HCOOH and H $_2$  were detected. Moreover, the Cu–Sn catalyst maintained long-term stability at least 14 h. The CO faradaic efficiency of OD-Cu catalyst increased with increasing the potential and reached a maximum ( $\approx 63\%$ ) at  $-0.6$  V vs. RHE and then drop to 32% at  $-0.8$  V vs. RHE. In comparison, HCOOH faradaic efficiency increased along with increasing overpotential, reaching 45% FE at  $-0.8$  V vs. RHE. On the other hand, Sn deposited on Sn electrode showed completely H $_2$  production. In addition, the authors have elucidated the effect of Sn deposition amount on the pre-reduced OD-Cu. The optimal amount of Sn was obtained at 3.9  $\mu\text{mol cm}^{-2}$ , achieving selectivity of 90% CO FE and 5% HCOOH FE at  $-0.6$  V vs. RHE; however, the excess of Sn deposited on OD-Cu favored H $_2$  generation. In order to investigate the catalytic performance of core-shell Cu–SnO $_2$

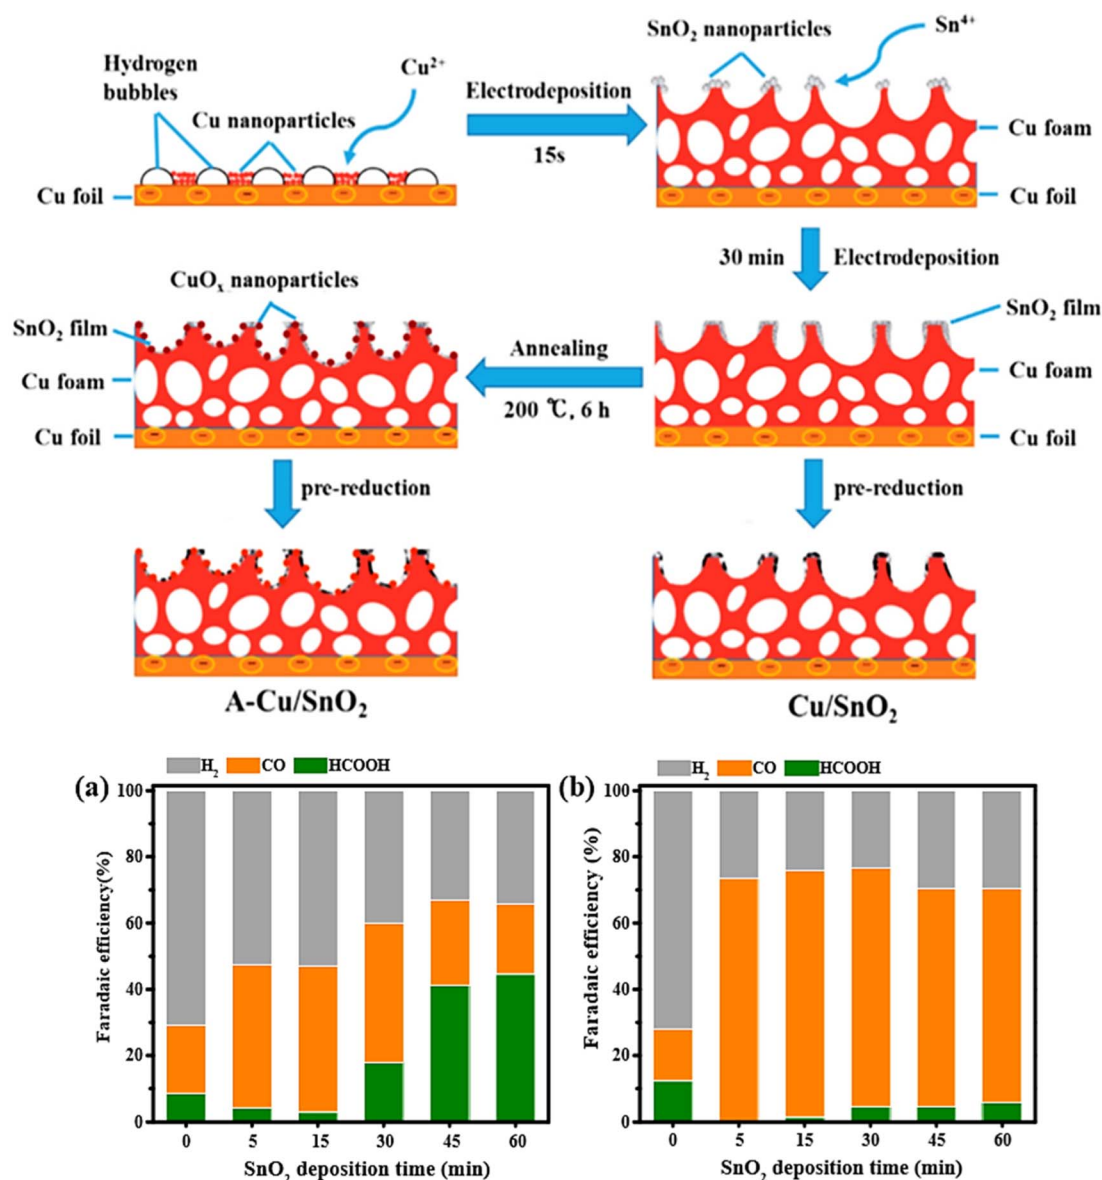


Fig. 5 (Up) Schematic drawing of the fabrication of Cu/SnO $_2$  and A-Cu/SnO $_2$ . (Bottom) Comparison of faradaic efficiencies of H $_2$ , CO, and HCOOH for (a) Cu/SnO $_2$  and (b) A-Cu/SnO $_2$  electrodes with different deposition times at  $-1.0$  V vs. RHE in CO $_2$ -saturated 0.1 M KHCO $_3$ .<sup>73</sup>

nanoparticles, Li *et al.*<sup>72</sup> synthesized two types of CuSnO<sub>2</sub> nanoparticles with the same core radius (7 nm) but different SnO<sub>2</sub> shell thicknesses (0.8 nm and 1.8 nm). They found that the thickness of Sn shell has a significant effect on product selectivity. The nanoparticles with thinner SnO<sub>2</sub> shell 0.8 nm (Fig. 5a) reached a maximum FE of 93% toward CO at  $-0.7$  V *vs.* RHE with a current density of  $4.6 \text{ mA cm}^{-2}$ . The nanoparticles with thicker SnO<sub>2</sub> shell 1.8 nm (Fig. 5b) could produce 85% HCOO<sup>−</sup> at  $-0.9$  V *vs.* RHE and less than 1% of CO formation. Based on density functional theory (DFT) calculations, the high selectivity of 0.8 nm SnO<sub>2</sub> shell toward CO was ascribed to the large compressive strain on the surface (10%), Cu doping on 0.8 nm SnO<sub>2</sub>, and the less negative overpotential for CO ( $-1.87$  V *vs.* RHE) compared to HCOO<sup>−</sup> ( $-2.21$  V *vs.* RHE). To investigate the activity and the selectivity of Sn–Cu catalysis toward CO<sub>2</sub> reduction, Li *et al.*<sup>73</sup> engineered Cu/SnO<sub>2</sub> electrode by electrodepositing SnO<sub>2</sub> films on porous copper foam followed by electrochemical pre-reduction. The same procedure was used to fabricate the A-Cu/SnO<sub>2</sub> electrode, but with an additional annealing step. The Cu foil was mechanically polished with 200-grade sandpaper, electropolished in 85% of phosphoric acid, and washed with acetone and deionized water. Epoxy resin was used to encapsulate the back of Cu foil. The Cu foam was deposited on the pretreated Cu foil at a current density of  $-3 \text{ A cm}^{-2}$  for 15 s in a plating bath containing (0.2 M CuSO<sub>4</sub>, 1.5 M H<sub>2</sub>SO<sub>4</sub>). The Sn foil (2 cm × 2 cm) was electrodeposited on Cu foam electrode *via* electrodeposition method using a constant potential of  $-0.3$  V while varying deposition time (5, 15, 30, 45, and 60 min) in the electrolyte consisting of (0.02 M SnCl<sub>4</sub>, 0.1 M NaNO<sub>3</sub>, 0.075 M HNO<sub>3</sub>). The electrochemical pre-reduction was carried out in a CO<sub>2</sub>-saturated 0.1 M KCO<sub>3</sub> at  $-0.5$  V *vs.* RHE for 1 h. The resultant electrode was labeled as Cu/SnO<sub>2</sub> electrode. A-Cu/SnO<sub>2</sub> electrode was obtained by applying an additional annealing step (200 °C for 6 h in muffle furnace) between electrodepositing and pre-reduction processes (Fig. 5).

For the electrocatalytic performance, Cu/SnO<sub>2</sub> and A-Cu/SnO<sub>2</sub> were evaluated under a wide potential range (from  $-0.8$  V to  $-1.2$  V *vs.* RHE). The Cu/SnO<sub>2</sub> catalyst achieved 75% of H<sub>2</sub> FE and 25% of CO FE at  $-0.8$  V *vs.* RHE. In contrast, A-Cu/SnO<sub>2</sub> exhibited a higher selectivity reaching nearly 60% FE at  $-0.8$  V *vs.* RHE and a significant decrease of FE of H<sub>2</sub> approximately 40% at  $-0.8$  V. This comparison indicated that A-Cu/SnO<sub>2</sub> has not only higher selectivity toward CO than Cu/SnO<sub>2</sub>, but also higher CO<sub>2</sub> reduction activity. Furthermore, the authors investigated the effect of SnO<sub>2</sub> deposition time on Cu foam for both electrodes Cu/SnO<sub>2</sub> and A-Cu/SnO<sub>2</sub> at  $-1.0$  V *vs.* RHE. In the case of Cu/SnO<sub>2</sub> electrodes, the efficiency of HCOOH increased with increasing the deposition time reaching the maximum at 60 min, while H<sub>2</sub> efficiency decreased along with increasing the deposition time. In contrast, CO FE achieved a higher level at 30 min and then decreased dramatically at 45 min of SnO<sub>2</sub> deposition time, and has since continued to decline. For A-Cu/SnO<sub>2</sub> with different deposition times of SnO<sub>2</sub>, the production selectivity remained almost constant at greater than 70% FE for CO, and the least formation product was for HCOOH with FE (<5%), with a remarkable suppression of hydrogen evolution reaction. In terms of stability, A-Cu/SnO<sub>2</sub> catalyst with a deposited time of

15 min exhibited long-term stability of about 10 h. The selectivity for CO was maintained around 75% during the 10 h electrolysis, and the total current density was kept well at  $-8.5 \text{ mA cm}^{-2}$ .

This class of bimetallic is very interesting as it can be tuned by different synthesis method to prepare active electrode for CO<sub>2</sub>RR. However, one of the main drawbacks of these Cu–Sn materials is their shortcoming to further reduce CO<sub>2</sub> to multi-carbon hydrocarbons and other oxygenates value added chemicals. Accordingly, these materials do not offer a promising way to obtain a clean renewable fuel of high energy density and close the carbon loop cycle. The main products of Cu–Sn are carbon monoxide and formic acid or it can be tuned from one to another by varying the Cu/Sn composition.<sup>74</sup> This is barrier towards viable utilization of these materials for CO<sub>2</sub> valorization to C2 and oxygenates.

### 3.2 Cu–In bimetallic materials

Luo *et al.*<sup>75</sup> synthesized Cu–In catalyst by simply depositing In<sup>3+</sup> on Cu(OH)<sub>2</sub> NWs followed with mild oxidation and *in situ* electroreduction treatments. The Cu(OH)<sub>2</sub> nanowires were synthesized *via* simple chemical oxidation. For this purpose, Cu foil (1 cm × 1 cm) was cleaned with water and sonicated in acetone for 5 min. Then, it was further etched in a solution containing 2 M of HNO<sub>3</sub> for 5 min to remove surface impurities. After immersing the Cu foil in a solution consisting of (2.5 M NaOH, 0.125 M (NH<sub>4</sub>)<sub>2</sub> S<sub>2</sub>O<sub>8</sub>) for 10 min to grow Cu(OH)<sub>2</sub> NWs, the color of the solution changed from reddish to dark cyan, indicating the formation of Cu(OH)<sub>2</sub> NWs.<sup>76</sup> Tin (In) was deposited by dipping Cu foil into a solution containing InCl<sub>3</sub> for 30 s. The catalyst was obtained by *in situ* electroreduction before the CO<sub>2</sub> electroreduction experiments.

The electrocatalytic performance showed that the CO faradaic efficiency of CuNWs has increased gradually reaching the maximum (45%) at  $-0.6$  V before dropping significantly to 16% at  $-1.0$  V. HCOOH selectivity increased steadily along with decreasing the applied potential reaching the highest FE at  $-0.9$  V and then decreased gradually at  $-1.0$  V. While H<sub>2</sub> exhibited a high FE > 50% at a potential between ( $-0.4$  to  $-0.5$  V).

In contrast, the CuIn<sub>20</sub> catalyst produced CO as a main product throughout the entire examined potential range. Thus, CO FE of CuIn<sub>20</sub> reached almost 95% in the range of  $-0.6$  to  $-0.8$  V.

The current density measurements of Cu NWs and CuIn<sub>20</sub> under potentiostatic conditions showed that the CO partial current density of CuIn<sub>20</sub> was 5 times higher than that of Cu NWs catalyst. The stability test of CuIn<sub>20</sub> and Cu NWs was carried out at an applied potential of  $-0.6$  V. Initially, Cu NWs catalyst exhibited 50% CO FE and dropped to 32% after 12 h of operation. Whereas, the CuIn<sub>20</sub> catalyst exhibited a stable current density of nearly  $1.7 \text{ mA cm}^{-2}$  and maintained an average (90%) of CO FE in the span of 60 h. According to the authors, the long-term stability of CuIn<sub>20</sub> catalyst could be ascribed to its low sensitivity to metal impurities.

The role of the In deposition amount on the CO<sub>2</sub>RR was studied by immersing Cu NWs in various concentrations of





Fig. 6 (a) The current density of OD-Cu and Cu-In, (b) faradaic efficiencies of OD-Cu, (c) faradaic efficiencies of Cu-In, (d) test stability for the Cu-In catalyst at  $-0.6$  V vs. RHE in  $0.1$  M  $\text{KHCO}_3/\text{CO}_2$ . Reproduced with permission.<sup>77</sup> Copyright ©2015, Wiley-VCH.

$\text{InCl}_3$  solution. The result showed that the current density and CO faradaic efficiency depended strongly on the In amount. It was found that CO FE increased with increasing In amount ( $0.52 \mu\text{mol cm}^{-2}$ ) reaching a maximum of approximately 93% for  $\text{CuIn}_{20}$  catalyst and then decreased for a higher amount of In.

Rasul *et al.*<sup>77</sup> developed a highly selective Cu-In electrocatalyst for the electrochemical reduction of  $\text{CO}_2$  to CO. The Cu foil ( $1 \text{ cm} \times 3 \text{ cm}$ ) was cleaned in  $1 \text{ M HCl}$  for several seconds, rinsed with Milli-Q water, and dried at room temperature. The foil was further dried with Kimwipes to avoid partial oxidation of the electrode. OD-Cu electrode was obtained by thermally oxidizing Cu metal sheet at  $500^\circ\text{C}$  for 2 h under static air in a muffle furnace. Afterward, Cu-In electrode was obtained through the *in situ* electrochemical reduction of the OD-Cu electrode in a solution consisting of ( $0.05 \text{ M InSO}_4$ ,  $0.4 \text{ M citric acid}$ ) at a current density of  $-10 \text{ mA}$  for 90 min.

The electrocatalytic performance of In-Cu and OD-Cu catalysts was investigated under a wide potential range potential from ( $-0.3$  to  $-0.7 \text{ V vs. RHE}$ ). The results indicated that OD-Cu catalysts (Fig. 6b) produced mainly  $\text{H}_2$  at  $-0.3 \text{ V}$ . However, CO

and HCOOH selectivity increased along with increasing the applied potential and reached a maximum of 40% and 30%, respectively, at  $-0.6 \text{ V vs. RHE}$ . In contrast, Cu-In electrode (Fig. 6a) exhibited a CO selectivity of 23% and a negligible  $\text{H}_2$  level at  $-0.3 \text{ V vs. RHE}$ . The conversion of  $\text{CO}_2$  to CO increased with more negative polarization of the electrode, reaching a maximum faradaic efficiency of 95% at  $-0.7 \text{ V vs. RHE}$ .

Cu-In and OD-Cu catalysts (Fig. 6c) exhibited similar values for total current density in the same electrochemical conditions. On the other hand, the stability of Cu-In catalyst (Fig. 6d) was evaluated at  $-0.6 \text{ V}$  in  $0.1 \text{ M KHCO}_3$ , indicating good stability for 7 h with 85% CO FE.

### 3.3 Cu-Pd bimetallic materials

Palladium is as an intriguing catalyst owing to its low barrier toward  $\text{H}_2$  adsorption and ease of formation of the metal hydride ( $\text{PdHx}$ ).<sup>78-81</sup> It is regarded as a promising candidate for catalyzing  $\text{CO}_2$  hydrogenation reactions and electrochemical  $\text{CO}_2$  reduction reactions because it facilitates the hydrogenation and gives mainly CO in  $\text{CO}_2\text{RR}$  due to the hydride formation,



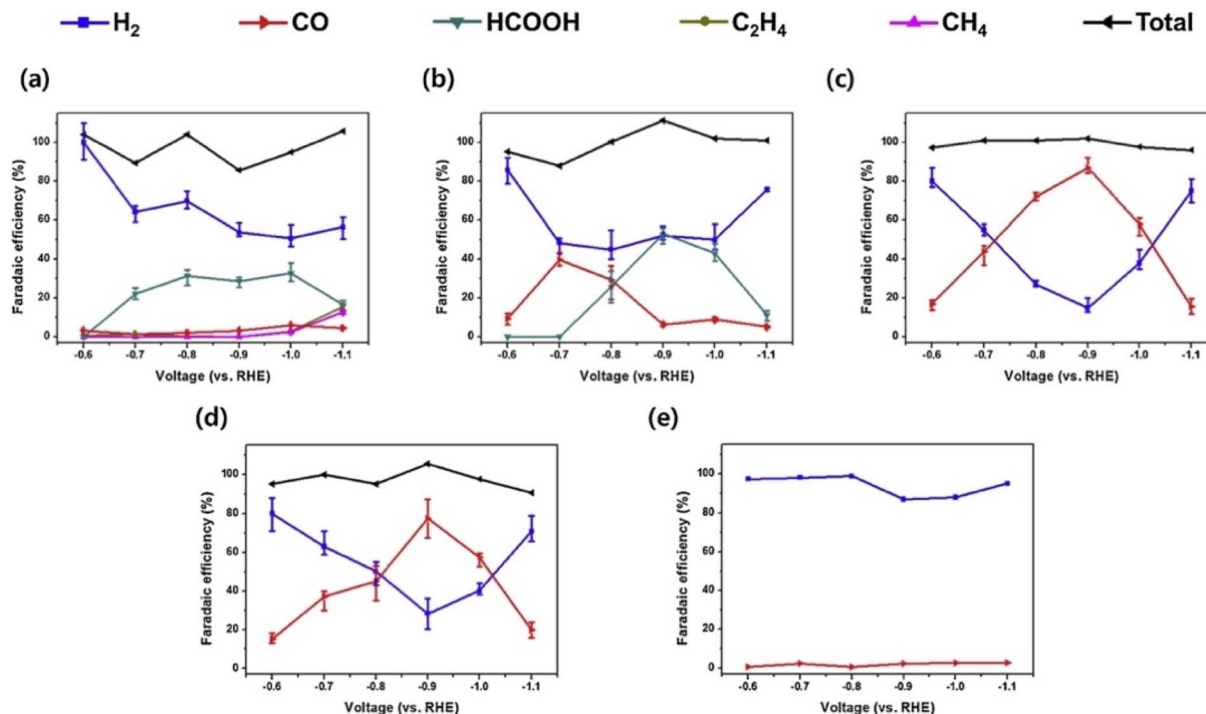


Fig. 7 Faradaic efficiencies of the Cu–Pd NP/C catalysts in 0.1 M  $\text{KHCO}_3$  solution: (a) Cu NP/C, (b)  $\text{Cu}_3\text{Pd}$  NP/C, (c) CuPd NP/C, (d)  $\text{CuPd}_3$  NP/C, and (e) Pd NP/C. Reproduced with permission.<sup>84</sup> Copyright ©2019, Elsevier.

which inhibits  $\text{CO}^*$  binding and affects selectivity toward  $\text{COH}^*/\text{CHO}^*$  for further  $\text{CO}_2\text{RR}$   $\text{C}_2$  byproducts.<sup>48,82</sup>

For  $\text{CO}_2\text{RR}$ , Mun *et al.*,<sup>83</sup> have prepared monodisperse Cu–Pd nanoparticles (NPs) with various compositions *via* a colloidal method. Different products were obtained for when comparing with bulk copper catalyst. It was observed that alloying Cu to Pd suppresses hydrocarbon evolution and leads to CO production with a 1 : 1 Cu–Pd being the best electroactive catalyst giving 87% CO at  $-0.9$  V vs. RHE (Fig. 7). The DFT results indicate that alloying Pd to Cu enhances the energy barrier of the CO protonation step, which is the potential-determining step for hydrocarbon production, resulting in a change in  $\text{CO}_2\text{RR}$  selectivity: Pd alloying causes  $\text{H}^*$  to be more firmly adsorbed on CuPd(211) than on Cu(211), and the energy binding of adsorbed  $\text{H}^*$  on Cu–Pd alloy is much lower energy than that of Cu(211), indicating that the HER is suppressed. The limiting potential of the favored  $\text{CO}^*$  protonation step is higher on CuPd(211) ( $-1.03$  V) than on Cu(211) ( $-0.60$  V) and as reported elsewhere<sup>50,82,84</sup> the  $\text{HCO}^*$  formation is much more favored than  $\text{COH}^*$  formation on Cu(211), and on CuPd(211). This indicates the hydrocarbon suppression on Cu–Pd alloy.

Recently, Xie and coworkers<sup>85</sup> have prepared Cu–Pd heterostructures *via* dual potential electrochemical deposition which promotes  $\text{CO}_2$  reduction and stabilizes  $\text{CO}^*$  to preferable  $\text{CH}_4$  formation. A small amount of  $\text{HCOOH}$  and  $\text{C}_2\text{H}_4$  were observed. The aforementioned heterostructure exhibited a higher  $\text{CO}_2$ -to- $\text{CH}_4$  selectivity of 32% at high potentials of  $-1.2$  and  $-1.25$  V vs. RHE compared to the bare Cu and Pd metals. Using the DFT calculations, it was determined that adsorbed CO is the key

intermediate for  $\text{CH}_4$  and  $\text{C}_2\text{H}_4$  production which was in agreement with previous reports.<sup>86,87</sup>

A pyridine derivative abbreviated PYD was entrapped in Cu–Pd alloy to prepare and organically PYD@Cu–Pd composite for the  $\text{CO}_2\text{RR}$  to combine two active sites for alcohols electrosynthesis in a single catalyst. Cu nanoparticles (NPs), Pd NPs, Cu–Pd alloy, PYD@Cu and PYD@Pd composite were also prepared and tested as control experiments.<sup>88</sup> The PYD@Cu–Pd gives 26% and  $\text{C}_2\text{H}_5\text{OH}$  with 12% faradaic efficiencies at  $-0.04$  and  $-0.64$  V vs. RHE, respectively. Remarkably, the PYD@Pd and Cu–Pd yielded respectively 35% faradaic efficiency of  $\text{CH}_3\text{OH}$  at  $-0.04$  V vs. RHE and 11% of  $\text{C}_2\text{H}_5\text{OH}$  at  $-0.64$  V vs. RHE. This means that the PYD@Cu–Pd catalyses  $\text{CO}_2$  to both  $\text{CH}_3\text{OH}$  and  $\text{C}_2\text{H}_5\text{OH}$  using two active regions: Cu–Pd (For  $\text{C}_2\text{H}_5\text{OH}$ ) and pyridine ring of PYD@Pd to PYD  $\text{H}^*$  ( $\text{CH}_3\text{OH}$ ).<sup>89</sup> Other control catalysts did not lead to alcohol formation. Longer stability screening for the PYD@Cu–Pd composite at constant cathodic potential of  $-0.04$  and  $-0.64$  V vs. RHE was reported for 14 h. The current density remained constant for both potential values, reaching  $21 \text{ mA cm}^{-2}$  and  $5 \text{ mA cm}^{-2}$  for  $\text{CH}_3\text{OH}$  and  $\text{C}_2\text{H}_5\text{OH}$  production, respectively, throughout the test. Moreover, the  $\text{CH}_3\text{OH}$  FE could maintain around 25% for 15 times repeated electrolysis and a small drop on the faradaic efficiency to  $\text{C}_2\text{H}_5\text{OH}$  was observed throughout the 15 cycles. This work shows the importance of the synergic effect of gathering organic catalyst and metal alloy in a very engineered fashion to put in work two alcohol sites for the  $\text{CO}_2\text{RR}$ .

Whereas, Wang and coworkers<sup>90</sup> have investigated the CuPd alloy with Pd rich surface supported on carbon for the  $\text{CO}_2\text{RR}$  to

$\text{HCOO}^-$  with 2 electron transfer. The prepared  $\text{Cu}_{20}\text{Pd}_{80}/\text{C}$  catalyst using adsorbate-induced surface segregation method shows a modest faradaic efficiency for the  $\text{HCOO}^-$  electrosynthesis of 7.37%. When the same catalyst composition was prepared using by the  $\text{NaH}_2\text{PO}_2$  reduction solution method instead of the  $\text{H}_2$  thermal reduction process, the faradaic efficiency for  $\text{HCOO}^-$  production increased to 60% at  $-0.75$  V vs.  $\text{Ag}/\text{AgCl}$ . The authors have confirmed using *ex situ* XPS that the catalytic activity of the catalyst can be attributed to the lower bonding strength of  $\text{H}^*$  (adsorbed hydrogen) on the  $\text{Cu}_{20}\text{Pd}_{80}/\text{C}$  surface, which is promoted by the ligand effect between Cu and Pd as confirmed by the opposite band energy shift on  $\text{Pd } 3d_{5/2}$

and  $\text{Cu } 2p_{3/2}$  as well as the upshift of the d-band center for  $\text{Cu}_{20}\text{Pd}_{80}/\text{C}$  NPs. Then, the lower bonding strength of hydride on the surface catalyst would reduce the activation energy barrier of the catalyst to transfer hydrogen from its surface to  $\text{CO}_2$  and to form the  $\text{HCOO}^*$  intermediate. Long-term chronoamperometry of 140 h have led to the CO catalyst poisoning and deactivation.

Carbon monoxide electroformation from  $\text{CO}_2\text{RR}$  was reported by Chen *et al.*,<sup>91</sup> using bimetallic Cu–Pd nanoalloys with different compositions and morphologies: spherical (noted as S) Cu–Pd nanoalloys with Cu/Pd molar ratio of 1/0.3 have the highest faradaic efficiency toward CO conversion (93%), while



Fig. 8 LSV curves (a) of bimetallic Cu–Pd–S, Cu–Pd–0.1, Cu–Pd–C, Cu–Pd–0.3, Cu–Pd–D, Cu–Pd–0.8 nanoalloys, commercial Pd/C catalyst in  $\text{CO}_2$  saturated  $0.5 \text{ M KHCO}_3$  solution with a scan sweep of  $10 \text{ mV s}^{-1}$ , the CO faradaic efficiency at different applied potentials (b–d), the CO and  $\text{H}_2$  faradaic efficiency at a fixed potential of  $-0.87$  V (e), and CO partial current density of these nanoalloys (f). Reproduced with permission.<sup>91</sup> Copyright ©2018, American Chemical Society.

the dendritic Cu-Pd nanoalloys (noted as D) have the highest faradaic efficiency for H<sub>2</sub> (65.2%) *via* hydrogen evolution reaction at a polarized potential of  $-0.87$  V *vs.* RHE (Fig. 8). While the concave nanocubes of Cu-Pd-C (noted as C) shows much lower CO FE. This work has shed light on the effect of morphologies on CO<sub>2</sub>RR electroconversion, this will pave the way towards to catalysis by design and morphology dependent activity.

C<sub>2</sub> byproducts can be also formed through direct CO<sub>2</sub>RR. For instance, Feng and coworkers<sup>92</sup> have prepared Cu-Pd catalysts using simple electrodeposition method on carbon paper. The electrochemical CO<sub>2</sub>RR performance of the Cu-Pd/CP outperforms the bare Cu/CP and Pd/CP leading to higher current density suggesting favorable bonding and CO<sub>2</sub> activation. The faradaic efficiency of C<sub>2</sub>H<sub>4</sub> reached 45.23%, at  $-1.2$  V *vs.* RHE, whereas, Cu/CP recorded only 30% and no C<sub>2</sub>H<sub>4</sub> on Pd/Pd catalyst. This reported C<sub>2</sub>H<sub>4</sub> efficiency outperformed the state-of-the art metal catalysts reported elsewhere.<sup>93–96</sup> Ma *et al.*<sup>97</sup> investigated the effect of geometric arrangement on the Cu-Pd activity and selectivity. To this end, the authors synthesized different bimetallic Pd-Cu catalysts with disordered, ordered, and phase-separated atomic arrangements.

The electrocatalytic performance of CuPd bimetallic nanoparticles with distinct geometric arrangements exhibited different selectivity toward C<sub>1</sub> and C<sub>2</sub> products. For the ordered CuPd nanoparticles the faradaic efficiency toward C<sub>1</sub> products (mainly CO) achieved 80%, while C<sub>2</sub> products exhibited the lowest FE < 5%. However, the disordered CuPd nanoparticles reached a higher FE for CH<sub>4</sub> the ordered or phase-separated nanoparticles. In contrast, the phase-separated exhibited the highest FE 50% toward C<sub>2</sub> products (primarily C<sub>2</sub>H<sub>4</sub>). This could be due to the fact that the binding \*CO in the phase-separated is less affected by the segregation of the two sites. Regarding the current density measurements, the phase-separated sample exhibited the highest total current density of 370 mA cm<sup>-2</sup>, while the ordered sample achieved the lowest total current density. Furthermore, the authors investigated the correlation between the catalyst composition and its activity and selectivity. Therefore, they prepared two samples with different (Cu : Pd) ratios for the disordered structure: Cu<sub>3</sub>Pd and CuPd<sub>3</sub>. The electrochemical characterization showed that the CH<sub>4</sub> FEs for disordered CuPd were higher than that for both Cu<sub>3</sub>Pd and CuPd<sub>3</sub>. In addition, the FEs of C<sub>2</sub> products increased along with increasing Cu concentration.

Zhang *et al.*<sup>98</sup> reported an electrodeposition strategy for designing highly dispersed, ultrafine PdCu catalysts. PdCu catalyst exhibited a greater than two-fold enhancement in FE for CO<sub>2</sub> reduction to CH<sub>4</sub> as compared to the Cu catalyst. The maximum FE for CH<sub>4</sub> was 33% at  $-1.8$  V (*vs.* Ag/AgNO<sub>3</sub>). They indicated that the improvement was originated from a synergistic reaction between the Cu-CO and Pd-H sites during electrochemical CO<sub>2</sub> reduction. The onset of CO<sub>2</sub> reduction to CH<sub>4</sub> at the PdCu catalyst appeared at  $\sim 400$  mV and  $\sim 200$  mV more positive than at the Pd and Cu catalysts, respectively.

Chen *et al.*<sup>99</sup> prepared nanostructured Cu<sub>2</sub>O-derived Cu catalyst and PdCl<sub>2</sub> for CO<sub>2</sub> to C<sub>2</sub>H<sub>6</sub> conversion. The Cu<sub>2</sub>O-derived Cu catalyst was prepared by the electrochemical

deposition on Cu discs. When the addition of PdCl<sub>2</sub> was added into the catholyte during the CO<sub>2</sub> reduction at  $-1.0$  V (*vs.* RHE), the C<sub>2</sub>H<sub>6</sub> formation could be achieved with an FE of 30.1% at the same potential. According to their mechanistic studies, C<sub>2</sub>H<sub>4</sub> was first produced from CO<sub>2</sub> reduction at the Cu sites. The hydrogenation occurred with the help of adsorbed PdCl<sub>x</sub> to produce C<sub>2</sub>H<sub>6</sub>. The efficient conversion of C<sub>2</sub>H<sub>4</sub> to C<sub>2</sub>H<sub>6</sub> required both copper and PdCl<sub>x</sub> sites. However, adding of other palladium-based particles to the electrolyte, such as Pd<sup>0</sup>, PdO, or Pd-Al<sub>2</sub>O<sub>3</sub>, did not reach the same conversion efficiency.

Zhu *et al.*<sup>100</sup> employed thermal reduction treatment and *in situ* growth to prepare the CuPd catalyst. According to the electrocatalytic results, the FE of CuPd(100) catalyst achieved 50.3% at  $-1.4$  V *vs.* RHE, which was higher than that of the Cu catalysts (23.6%) at the same potential. The CuPd(100) catalyst also had the highest electrochemically active surface area of  $7.04 \times 10^{-3}$  mF cm<sup>-2</sup>. These results were consistent with the DFT prediction, implying that CuPd(100) could provide enough CO\* for the C-C coupling by lowering the energy barrier of the CO<sub>2</sub>\* hydrogenation step.

Lai *et al.*<sup>101</sup> used a pulse program consisting of an open-circuit voltage (OCV) and a cathodic potential to investigate the effect of spontaneous reoxidation on the catalytic performance of Cu-Pd bimetallic catalysts. The results showed that the simultaneous presence of Cu and Pd was critical for achieving high CO FE for the bimetallic catalysts. Among all Cu-Pd catalysts, the Cu<sub>5</sub>Pd<sub>5</sub> reached the maximum FE of 88% with the partial current density of  $-132$  mA h g<sup>-1</sup> at an applied cathodic potential of  $-0.7$  V for 210 s and anodic potential at OCV for 450 s. The DFT calculation suggested that such efficient CO<sub>2</sub> conversion to CO resulted from the reduced \*CO binding strength.

Li *et al.*<sup>102</sup> constructed a novel Cu-Pd catalyst Cu@PIL@Pd by impregnating PdCl<sub>2</sub> into the Cu@PIL with Cl<sup>-</sup> as the anion. It was found that the Cu@PIL@Pd-2 catalyst exhibited the highest FE toward C<sub>2+</sub> of 68.7% with a high partial current density of 178.3 mA cm<sup>-2</sup> at a cathodic potential of  $-1.01$  V *vs.* RHE. The catalyst also showed the highest CH<sub>4</sub> FE of 42.5% with a partial current density of 172.8 mA cm<sup>-2</sup> at  $-1.24$  V *vs.* RHE. The authors attributed the high selectivity of the Cu@PIL@Pd-2 catalyst toward C<sub>2+</sub> products to the synergy effect between the adjacent Pd and Cu sites. The Cu was found to promote the CO generation on the Pd sites, while the abundant Cu-Pd interfaces promoted the \*CO spillover from Pd sites to adjacent Cu sites, promoting the C-C coupling reaction.

Shen *et al.*<sup>103</sup> investigated CO electroreduction on a series of Cu-Pd catalysts prepared with different compositions: Cu<sub>70</sub>Pd<sub>30</sub>, Cu<sub>49</sub>Pd<sub>51</sub>, and Cu<sub>23</sub>Pd<sub>77</sub>. The results showed that the Cu<sub>70</sub>Pd<sub>30</sub> catalyst produced acetate with a FE of >14% at  $-0.5$  V *vs.* RHE and ethanol with a FE of 29% at  $-1.2$  V *vs.* RHE. For the Pd-rich Cu<sub>23</sub>Pd<sub>77</sub> catalyst, H<sub>2</sub> was the main product with a FE of >40% throughout the investigated potential range. In contrast, the Cu<sub>49</sub>Pd<sub>51</sub> achieved a high selectivity toward acetate with a FE of >65% at  $-1.2$  V *vs.* RHE. The acetate selectivity of Cu<sub>49</sub>Pd<sub>51</sub> in the alkaline electrolyte was explained by the asymmetrical C-C coupling mechanism *via* \*CO-\*CHO coupling.



### 3.4 Cu-Zn bimetallic materials

Zinc (Zn) is environmentally friendly and less expensive as compared to other co-catalysts such as Ag, Pd, and Au.<sup>104</sup> Zn has attracted more attention due to its ability to reduce CO<sub>2</sub> to CO, HCOOH, and syngas at different overpotential.<sup>105,106</sup>

Because hydrogen evolution reaction occurs more slowly on Zn electrodes than on Cu electrodes,<sup>107</sup> forming bimetallic Cu-Zn catalyst is one approach to enhance the electrocatalytic activity of Cu electrode toward CO<sub>2</sub> reduction and promotes multicarbon products. Ren *et al.*<sup>108</sup> prepared a series of oxide-

derived Cu<sub>x</sub>Zn catalysts to promote the reduction of CO<sub>2</sub> to C<sub>2</sub>H<sub>5</sub>OH. They revealed that introducing a co-catalyst improved the selectivity and the efficiency of CO<sub>2</sub> reduction.

Cu<sub>x</sub>Zn oxide films were prepared by dissolving 0.3 M CuSO<sub>4</sub> and 2.3 M lactic acid in ultrapure water. NaOH was added to the solution to adjust the pH to 12, 10.6, or 9. Then 10 mM of ZnCl<sub>2</sub> was added to the solution. The oxide films Cu<sub>x</sub>Zn were deposited onto Cu disks using a current density of  $-0.92 \text{ mA cm}^{-2}$  for 10 min. During the deposition process, the electrolyte was kept at 960 °C and stirred at 300 rpm. The Cu<sub>x</sub>Zn catalysts exhibited



Fig. 9 Operando Raman spectrum of (a and b) Cu catalyst and (c) CuZn catalyst at different potentials in 0.1 M KHCO<sub>3</sub> under laser radiation at 785 nm; (d) partial current density (normalized against the electrochemical surface area) of C<sub>2</sub>H<sub>5</sub>OH, methane and carbon monoxide as a function of applied potential; (e) electrochemical reduction of acetaldehyde on Cu and CuZn catalyst; and (f) proposed mechanism of C<sub>2</sub>H<sub>5</sub>OH formation. Reproduced with permission.<sup>111</sup> Copyright ©2019, Wiley-VCH.

distinct selectivities toward  $C_2H_4$  and  $C_2H_5OH$  formation. The faradaic efficiency of  $Cu_xZn$  catalysts toward  $C_2H_5OH$  increased along with increasing the amount of Zn, achieving the maximum FE of 29.1% on  $Cu_4Zn$  at  $-1.05$  V vs. RHE. On the contrary, the faradaic efficiency toward  $C_2H_4$  decreased along with increasing Zn amount, achieving the lowest FE of 4.1% on  $Cu_2Zn$ .

At  $-1.05$  V vs. RHE,  $Cu_4Zn$  catalyst reached the highest partial current density of  $C_2H_5OH$  approximately  $-8.2$  mA  $cm^{-2}$ ,  $Cu_{10}Zn$  catalyst achieved a partial current density of almost  $-4.0$  mA  $cm^{-2}$  toward  $C_2H_5OH$ . Whereas  $Cu_2Zn$  exhibited the lowest partial current density of almost  $-2.3$  mA  $cm^{-2}$  toward  $C_2H_5OH$ . Furthermore,  $Cu_4Zn$  catalyst maintained remarkable stability toward  $C_2H_5OH$  with a faradaic efficiency of 29.1% in the span of 5 h. However, the FE of  $C_2H_5OH$  decreased to 25% for 10 h electrolysis. The authors proposed a mechanism to elucidate the electroreduction of  $CO_2$  to  $C_2H_5OH$ . In the first step,  $CO_2$  is reduced to  $*CO$  at Cu or Zn sites and is then reduced to  $CHO$  or  $CH_x$  ( $x = 1-3$ ) intermediates. Because of the weak adsorption of CO on Zn sites, desorbed CO could diffuse and overflow on the Cu sites. This CO could insert between Cu sites and  $*CH_2$  to form  $*COH_2$  which is further reduced to acetaldehyde and finally  $C_2H_5OH$ .

Keerthiga and Chetty<sup>109</sup> used a simple electrodeposition approach to design a hierarchically structured Zn electrocatalyst on Cu electrode. They prepared two samples Cu/Zn-A (in electrolytic bath containing 0.6 M of sodium zincate) and Cu/Zn-B (in electrolytic bath containing 6 M of sodium zincate). For the electrocatalytic performances, the prepared catalysts were evaluated under a wide potential range (from  $-0.7$  V to  $-1.8$  V vs. NHE). The Cu/Zn-B catalyst produced a maximum  $CH_4$  formation of 52%,  $C_2H_6$  formation of 24%, and  $H_2$  formation of 8.7% at a potential of  $-1.6$  V vs. NHE. Furthermore, the Cu/Zn-B catalyst exhibited a higher current density of  $0.70$  mA  $cm^{-2}$  for  $CH_4$  at a potential of  $-1.6$  V vs. NHE compared to the Cu ( $0.14$  mA  $cm^{-2}$ ) and Zn ( $0.01$  mA  $cm^{-2}$ ) electrodes. However, Cu/Zn-A catalyst produced mainly  $H_2$ , with only minor hydrocarbon formation. The results suggested that Zn deposition on Cu reduced hydrogen evolution and favored the addition of protons to form  $CH_4$ . The porous nature of hierarchically structured Zn could allow the diffusion of  $CO_2$  through the Cu/Zn interface for the reduction while maintaining high catalytic activity due to the of the large electrode area of the hierarchical structure reducing the surface poisoning.

Su *et al.*<sup>110</sup> demonstrated the catalytic synergies of Cu and Zn to enhance the  $CO_2$  electroreduction towards liquid  $C_2$  products using hierarchically porous Cu/Zn catalysts.

The bimetallic catalysts were prepared based on an interfacial self-assembly method, in which the alloy composition of the catalysts can be adjusted by varying the ratios of metal precursors. The electrocatalytic performance results showed that hierarchically macroporous-mesoporous (HMMP)  $Cu_5Zn_8$  demonstrated a high  $C_2H_5OH$  selectivity of 46.6% with  $C_2H_5OH$  current density of  $-2.3$  mA  $cm^{-2}$  at  $-0.8$  V vs. RHE. The  $Cu_5Zn_8$  electrocatalyst maintained an excellent stability of 11 h towards  $CO_2$  electroreduction. Grätzel and coworkers<sup>111</sup> prepared CuZn bimetallic catalyst by applying 100 atomic layer deposition

cycles of ZnO precursor on CuO nanowires. The obtained CuZn bimetallic catalysts exhibited 32% FE for  $C_2H_5OH$  production and  $C_2H_5OH$  current density of  $-10.5$  mA  $cm^{-2}$  at  $-1.15$  V vs. RHE. Based on their understanding, the authors proposed a mechanism of  $C_2H_5OH$  formation on Cu and CuZn catalysts (Fig. 9). On Cu catalyst,  $C_2H_4$  and  $C_2H_5OH$  are produced through the dimerization of two adsorbed CO, resulting in the formation of  $C_2H_4$ . On CuZn catalyst, the CO produced on Zn sites tends to be released into the electrolyte due to the low binding energy between CO and Zn. At low overpotential, the formation of  $*CH_3$  intermediate is minimal, and most of CO is released as CO gas. At higher overpotential, the  $*CH_3$  intermediate is produced in large amounts and combines with the CO present near Cu sites to form  $C_2H_5OH$ .

Dongare *et al.*<sup>112</sup> engineered oxide derived CuO-ZnO<sub>x</sub> bimetallic catalysts *via* a simple co-precipitation method followed by an air atmosphere calcination step. The loading percentage of Cu to Zn in the electrocatalysts was adjusted by varying the precursor concentrations from  $x = 5$  to 20 wt%. The performance of the CuO-ZnO<sub>x</sub> electrocatalysts was investigated under a wide potential range from  $-0.4$  V to  $-1$  V vs. RHE. The CuO-ZnO<sub>x</sub> electrocatalysts demonstrated different FE for HCOOH,  $C_2H_5OH$ ,  $CH_3OH$ , and *n*-propanol depending on the precursor concentrations. The CuO electrode showed low selectivity for  $C_2H_5OH$  about 7.10% of FE. In contrast, incorporating ZnO into CuO improved  $C_2H_5OH$  selectivity while suppressing the formation of HCOOH. Interestingly, CuO-ZnO<sub>10</sub> electrode showed the highest faradaic efficiency of 22.27% for  $C_2H_5OH$  at  $-0.8$  V vs. RHE. While, further increase in Zn concentration decreased the FE of  $C_2H_5OH$  to approximately 16.41% for CuO-ZnO<sub>20</sub> electrode. Similar trend was found in the case of *n*-propanol and  $CH_3OH$ . The FE of *n*-propanol increased from 4.5% to 10.23% using CuO and CuO-ZnO<sub>10</sub> respectively at  $-0.6$  V vs. RHE, and the FE of  $CH_3OH$  increased from 7.44 to 15.02% on CuO and CuO-ZnO<sub>10</sub> electrodes at  $-0.6$  V vs. RHE. The authors claimed that the balanced CuO and ZnO percentage for maximum C-C coupling was responsible for the improved selectivity. The CuO-ZnO<sub>10</sub> electrode gave a balanced CO supply, resulting in increased CO dimerization. The ZnO provided additional CO to increase the local CO concentration on the Cu surface and as a result,  $*CO$  surface coverage, resulting in a faster conversion of CO-to- $C_2H_5OH$  products. Furthermore, increasing Zn concentration in the CuO-ZnO<sub>x</sub> electrode beyond 10% results in as oversupply of CO, which lowered the  $*CO$  dimerization.

The stability and long-term durability of CuO-ZnO<sub>10</sub> electrode was also investigated. During 12 hours of operation, the CuO-ZnO<sub>10</sub> electrode maintained a total current density of  $-3.75$  mA  $cm^{-2}$  with no change in the electrode morphology. The reproducibility experiments on CuO-ZnO<sub>10</sub> electrode revealed that the selectivity of  $C_2H_5OH$  was maintained for first three cycles but decreased for subsequent cycles.

### 3.5 Cu-Ag bimetallic materials

Hoang *et al.*<sup>113</sup> aimed to enhance  $CO_2$  selectivity towards  $C_2$  products such as  $C_2H_4$  and  $C_2H_5OH$ . For this purpose, Cu-Ag





Fig. 10 (a–c) FEs for each gaseous product and for the main liquid product over (a) Ag NPs, (b) Cu NPs, and (c) Ag<sub>1</sub>-Cu<sub>1.1</sub> NDs. (d and e) Total current density (d) and partial current density for the electroreduction of CO<sub>2</sub> (e) over Ag NPs, Cu NPs, and Ag<sub>1</sub>-Cu<sub>1.1</sub> NDs. (f) CO and C<sub>2</sub>H<sub>4</sub> mass activity of Ag NPs, Cu NPs and Ag<sub>1</sub>-Cu<sub>1.1</sub> NDs at -1.1 V vs. RHE. Reproduced with permission.<sup>114</sup> Copyright ©2018, American Chemical Society.

catalysts were electrodeposited at a constant current density of 4 mA cm<sup>-2</sup> in a plating bath containing 0.1 M CuSO<sub>4</sub>·5H<sub>2</sub>O + 3.5 diamino-1,2,4 triazole (DAT), with or without 1 mM Ag<sub>2</sub>SO<sub>4</sub>, at pH = 1.5 adjusted by using H<sub>2</sub>SO<sub>4</sub>. (1 cm × 2.5 cm) of carbon paper was activated by immersing it in concentrated HNO<sub>3</sub> for 60 min and used as a gas diffusion electrode before being electrodeposited with 2 C cm<sup>-2</sup> of CuAg. The catalytic activity and selectivity of Cu and CuAg catalysts during CO<sub>2</sub> electroreduction were evaluated in a flow electrolyzer. CO, C<sub>2</sub>H<sub>4</sub>, and C<sub>2</sub>H<sub>5</sub>OH were the major products using Cu-wire 0% Ag named (Cu-wire), CuAg-wire (6% Ag) electrodeposited with DAT named (CuAg-wire), and CuAg-wire (6% Ag) electrodeposited without DAT named (CuAg-poly).

The electrocatalytic results showed that the catalysts exhibited different activities and product selectivities in 1 M KOH electrolyte. The CuAg-poly catalyst exhibited the lowest

faradaic efficiency nearly 30% toward C<sub>2</sub>H<sub>4</sub> and 20% toward C<sub>2</sub>H<sub>5</sub>OH at -0.7 V vs. RHE. Furthermore, CuAg-poly catalyst exhibited a low current density approximately -20 mA cm<sup>-2</sup> toward CO, C<sub>2</sub>H<sub>4</sub>, and C<sub>2</sub>H<sub>5</sub>OH. Cu-wire catalyst achieved high faradaic efficiency as well as high current density toward C<sub>2</sub> products. The faradaic efficiency for C<sub>2</sub>H<sub>4</sub> increased along with increasing the potential reaching the maximum (40%) at low potential (-0.5 V vs. RHE), and C<sub>2</sub>H<sub>4</sub> current density reached -100 mA cm<sup>-2</sup> at -0.7 V vs. RHE. However, for the C<sub>2</sub>H<sub>5</sub>OH product, Cu-wire exhibited a faradaic efficiency of 20% at -0.5 V vs. RHE and a current density of -75 mA cm<sup>-2</sup> at -0.7 V vs. RHE. In contrast, CuAg-wire catalyst achieved both high FE (60%) toward C<sub>2</sub>H<sub>4</sub> and high C<sub>2</sub>H<sub>4</sub> current density about -180 mA cm<sup>-2</sup> at -0.7 V vs. RHE. This high FE of C<sub>2</sub>H<sub>4</sub> could be ascribed to the high pH solvent. Huang *et al.*<sup>114</sup> have prepared Ag-Cu nanodimers for CO<sub>2</sub>-to-CO reduction, authors performed





a synthesis Ag–Cu with different compositions. The catalytic activity enabled by the addition of Ag to Cu in the form of segregated nanodomains within the same catalyst accounts for a 3.4-fold increase in faradaic efficiency for C<sub>2</sub>H<sub>4</sub> and 2-fold increase in partial current density for CO<sub>2</sub> reduction when compared to the pure Cu counterpart. The FE of C<sub>2</sub>H<sub>4</sub> electro-synthesis reached around 40% at −1.1 V vs. RHE (Fig. 10).

The Cu–Ag alloy was also used by Wang *et al.*<sup>115</sup> as an interfacial catalyst for the electrochemical reduction of CO<sub>2</sub> to C<sub>2</sub>H<sub>4</sub>. The faradaic efficiency for C<sub>2</sub>H<sub>4</sub> formation reached over 42%, which is more than twice as high as that of pure Cu catalyst at −1.1 V vs. RHE. The Cu–Ag catalyst remains stable and produce steady state C<sub>2</sub>H<sub>4</sub> for 30 h electrolysis. The mechanism formation C<sub>2</sub>H<sub>4</sub> was explained by the steps as follows: (i) Ag nanoparticles capture CO<sub>2</sub>, (ii) CO<sub>2</sub> molecule accepts one proton and one electron to form \*COOH intermediate on Ag nanoparticle surface, (iii) \*COOH accepts one proton and one electron to form \*CO intermediate on Ag nanoparticle surface. (iv) Transfer of CO intermediate from Ag nanoparticle to Cu side *via* the Ag/Cu interface and finally (v) C<sub>2</sub>H<sub>4</sub> is formed by coupling two CO molecules.

Wang *et al.*<sup>116</sup> synthesized Cu–Ag bimetallic nanowire arrays as catalysts in three steps. First, thermal oxidation was used in ambient air to grow CuO/Cu<sub>2</sub>O nanowires on copper mesh. Then, in the presence of H<sub>2</sub>, thermal reduction was carried out to obtain Cu nanowires. Finally, the Cu–Ag bimetallic nanowires were produced *via* galvanic replacement between Cu nanowires and the Ag<sup>+</sup> precursor. This catalyst leads to a reduction of CO<sub>2</sub> to a multitude of C<sub>1</sub> and C<sub>2</sub> byproducts with HCOO<sup>−</sup> being the highest in faradaic efficiency at −0.6, −0.7 and −0.8 V vs. RHE. Interestingly, at −0.8 V CH<sub>3</sub>OH, C<sub>2</sub>H<sub>5</sub>OH and propanol were observed with small faradaic efficiency (around 8%).

Meyer's group<sup>117</sup> have succeeded to reduce CO<sub>2</sub> to acetate using monodispersed, ultrasmall Ag and Cu bimetallic nanoparticles on electrochemically polymerized poly-Fe(vbpy)<sub>3</sub>(PF<sub>6</sub>)<sub>2</sub> films. The authors showed that the 8 electrons transfer to produce acetate can be obtained using a ratio variation of Ag/Cu. The maximum faradaic efficiency for acetate production reached 21.2% at −1.33 V vs. RHE. The presence of Ag on the surface of the cluster pair Cu<sub>2</sub>–Ag<sub>3</sub> plays a crucial role in maximizing acetate production.

Whereas, Jaramillo's group<sup>118</sup> have prepared CuAg thin films using nonequilibrium Cu/Ag alloying by physical vapor deposition technique. The prepared thin films prepared were tested for CO<sub>2</sub> electroreduction, the faradaic efficiencies of different 2 electrons byproducts including H<sub>2</sub>, CO and HCOOH and further reduced (>2e<sup>−</sup>) hydrocarbon, alcohol, and carbonyl CO<sub>2</sub>RR products were analyzed. The films containing Cu-rich and Ag-rich phases with substantial nonequilibrium interphase miscibility demonstrated that Ag miscibility into Cu is an effective strategy to promote the electrocatalytic CO<sub>2</sub>R selectivity and activity toward liquid carbonyl products. This was attributed to lower surface binding energies of oxygen-containing intermediate species. The catalytic activity of CuAg *versus* Cu toward more reduced products was decreased, while the activity toward hydrocarbons and HER was significantly suppressed. The

decreasing activity and selectivity to hydrocarbons and suppressing hydrogen was explained to be due to the Ag doping which weakens the Cu binding energy of \*H species.

### 3.6 Summary of the performance of Cu-based catalysts for CO<sub>2</sub>RR

Catalyst	Conditions	Highlighted product with FE
CuSn core-shell NPs: <sup>65</sup>	0.1 M KHCO <sub>3</sub> , −0.7 V vs. RHE	
CuSn NPs/c-A		CO (70.1%)
CuSn NPs/c-AH		CO (45.1%)
CuSn NPs/c-H		CO (20.1%)
Sn/Cu-PVDF electrode <sup>66</sup>	0.1 M KHCO <sub>3</sub> , −0.9 V vs. RHE	CO (80%)
Cu–Sn core shell nanowire <sup>70</sup>	0.5 M KHCO <sub>3</sub> , −0.8 V vs. RHE	CO (90%)
Sn/OD-Cu <sup>71</sup>	0.1 M KHCO <sub>3</sub> , −0.6 V vs. RHE	CO (90%), HCOO <sup>−</sup> (5%)
Core-shell Cu–SnO <sub>2</sub> NPs <sup>72</sup>	0.5 M KHCO <sub>3</sub>	
0.8 nm thick	−0.7 V vs. REH	CO (93%)
1.8 nm thick	−0.9 V vs. RHE	HCOO <sup>−</sup> (85%)
A-Cu/SnO <sub>2</sub> (ref. 73)	0.1 M KHCO <sub>3</sub> , −1.0 V vs. RHE	CO (70%)
CuIn <sub>20</sub> (ref. 75)	0.1 M KHCO <sub>3</sub> , −0.6 V vs. RHE	CO (95%)
Cu–In electrode <sup>77</sup>	0.1 M KHCO <sub>3</sub> , −0.7 V vs. RHE	CO (95%)
Cu <sub>0.75</sub> In <sub>0.25</sub>	0.5 M NaHCO <sub>3</sub> , −0.7 V vs. RHE	CO (81%)
Cu <sub>4</sub> Zn <sup>119</sup>	0.1 M KHCO <sub>3</sub> , −1.05 V vs. RHE	C <sub>2</sub> H <sub>5</sub> OH (29.1%)
Cu <sub>5</sub> Zn <sub>8</sub> (ref. 120)	0.05 M KHCO <sub>3</sub> , −1.5 V vs. RHE	CO (80%)
Cu <sub>94</sub> Ag <sub>6</sub> (ref. 113)	1 M KOH, −0.7 V vs. RHE	C <sub>2</sub> H <sub>4</sub> (60%), C <sub>2</sub> H <sub>5</sub> OH <sub>5</sub> (25%)
Cu <sub>16</sub> Ag <sub>84</sub> (ref. 121)	0.5 M KHCO <sub>3</sub> , −0.83 V vs. RHE	CO (45%)
Ag <sub>57</sub> Cu <sub>43</sub> (ref. 121)	0.5 M KHCO <sub>3</sub> , −1.5 V vs. RHE	CO (40%)
Ag–Cu core-shell (surface Ag : Cu = 1 : 0.6)	0.1 M KHCO <sub>3</sub> , −1.06 V vs. RHE	CO (5%), CH <sub>4</sub> (18%), C <sub>2</sub> H <sub>4</sub> (25%)
Ag–Cu core-shell <sup>122</sup> (surface Ag : Cu = 1 : 7.63)	0.1 M KHCO <sub>3</sub> , −1.06 V vs. RHE	CO (82%)
Cu <sub>38</sub> Cd <sub>62</sub> (ref. 123)	0.05 M KHCO <sub>3</sub> , −1.12 V vs. RHE	CO (43%), HCOO <sup>−</sup> (10%)
Ordered CuPd <sup>97</sup>	1 M KOH, −0.55 V vs. RHE	CO (80%)
Phase separated CuPd <sup>97</sup>	1 M KOH, −0.75 V vs. RHE	CO (17%), C <sub>2</sub> H <sub>4</sub> (48%), C <sub>2</sub> H <sub>5</sub> OH (15%)
Disordered CuPd <sup>97</sup>	1 M KOH, −0.60 V vs. RHE	CO (60%), CH <sub>4</sub> (1%), C <sub>2</sub> H <sub>4</sub> (4%), C <sub>2</sub> H <sub>5</sub> OH (2%)
Pd <sub>85</sub> Cu <sub>15</sub> (ref. 124)	0.1 M KHCO <sub>3</sub> , −0.89 V vs. RHE	CO (86%)
<i>o</i> -AuCu <sup>125</sup>	0.1 M KHCO <sub>3</sub> , −0.77 V vs. RHE	CO (80%)
Cu@Au <sup>126</sup>	0.5 M KHCO <sub>3</sub> , −0.65 V vs. RHE	CO (30%)





## 4. Challenges and prospects

Over the next few decades, fossil fuels may remain the main energy source. Mitigating the impact of waste CO<sub>2</sub> emissions is still a key issue in modern society. Electrocatalytic CO<sub>2</sub> reduction provides an intriguing method for reducing CO<sub>2</sub>, by which CO<sub>2</sub> as a feedstock can be converted into fuel or value-added chemicals. Copper is a magic element that can give various CO<sub>2</sub>RR byproducts. Controlling, tuning and modulating Cu surfaces and Cu-based bimetallic materials is necessary to achieve stable multi-carbon (*i.e.* targeted product) production. Regardless of structural control, fundamental understanding of electrolyte engineering, cell design, pressure, temperature should be also elucidated to give the working state of Cu electrodes. In this review, we have discussed the mechanism of CO<sub>2</sub> electrochemical reduction on various copper-based catalytic materials and how certain factors determine the product distribution and its selectivity including synthesis method, modification, surface morphology and structure. Copper-based catalyst materials currently occupy an important position in electrolysis due to their exceptional properties. Efficient and robust copper-based materials have been successfully prepared through enhanced synthetic strategies. These efforts embody the most important areas to understand the basics of CO<sub>2</sub> reduction and contribute positively to the development of new bimetallic catalysts. Regardless of the important steps that have been made in this direction and the encouraging research labor and production, we still feel that these following prospects should be taken into account:

- Develop other or existing chemical synthesis and modification technique that requires a straightforward design of the active sites in the general catalysis by design procedure. Thusly, more exploration of the modification steps should be explored.
- Explore and investigate other metals as they can give a better energy efficiencies and selectivity, for instance Sultan and coworkers have developed Al<sub>2</sub>CuO<sub>4</sub> nanosheets uniformly covered with CuO nanoparticles giving high FE for ethylene (82.4%) and remarkable stability in reaction condition to 100 h; this material achieved high current density of 421 mA cm<sup>-2</sup> in a flow cell.<sup>127</sup>
- In depth-understanding of CO<sub>2</sub>RR mechanisms is still a challenging task due to the evolution of the active site and the reconstruction of Cu materials under reaction conditions.
- Apply advanced *operando* techniques and theoretical calculation methods are highly recommended to probe the oxidation state, the CO<sub>2</sub> activation, and possible reaction intermediates of the electrochemical synthesized Cu-based catalysts. This will help to reorient and guide synthesis researchers to efficiently prepare a desired active site for a given CO<sub>2</sub>RR byproduct as well as understanding the reaction mechanism and provide further guidance for the catalyst development.
- Tremendous efforts should be directed towards the design and construction of larger CO<sub>2</sub> electrolyzer pilots. It should be noted that the high currents of the electrolyzer as well as the overall energy efficiency are key requirements for further commercialization of this technology.

It is trustworthy to note that the catalytic activity and stability of the reported electrocatalysts are still far away from the industrialization that usually requires long-term stability of more than 1000 h at a high current density of over 200 mA cm<sup>-2</sup>.

## Author contributions

Otmame Zoubir: writing the draft, writing – review & editing, literature analysis. Lahoucine Atourki: writing – review & editing; project administration, supervision and validation. Hassan Ait Ahsaine: writing the draft, project administration; supervision and validation. Amal BaQais: writing – review & editing.

## Conflicts of interest

The author declares that he has no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## Acknowledgements

Authors thank all the involved institutions.

## References

- 1 N. S. Spinner, J. A. Vega and W. E. Mustain, *Catal. Sci. Technol.*, 2012, **2**, 19–28.
- 2 W. Zhu, B. M. Tackett, J. G. Chen and F. Jiao, *Top. Curr. Chem.*, 2018, **376**, 41.
- 3 N. Uemoto, M. Furukawa, I. Tateishi, H. Katsumata and S. Kaneco, *ChemEngineering*, 2019, **3**, 15.
- 4 M. Mondal, S. Khanra, O. N. Tiwari, K. Gayen and G. N. Halder, *Environ. Prog. Sustainable Energy*, 2016, **35**, 1605–1615.
- 5 W. C. Chueh and S. M. Haile, *ChemSusChem*, 2009, **2**, 735–739.
- 6 M. Mikkelsen, M. Jørgensen and F. C. Krebs, *Energy Environ. Sci.*, 2010, **3**, 43–81.
- 7 S. Bai, H. Qiu, M. Song, G. He, F. Wang, Y. Liu and L. Guo, *eScience*, 2022, **2**, 428–437.
- 8 C. Liu, J. J. Gallagher, K. K. Sakimoto, E. M. Nichols, C. J. Chang, M. C. Chang and P. Yang, *Nano Lett.*, 2015, **15**, 3634–3639.
- 9 M. Schreier, J. Luo, P. Gao, T. Moehl, M. T. Mayer and M. Grätzel, *J. Am. Chem. Soc.*, 2016, **138**, 1938–1946.
- 10 X. Chang, T. Wang and J. Gong, *Energy Environ. Sci.*, 2016, **9**, 2177–2196.
- 11 Z. Cao, D. Kim, D. Hong, Y. Yu, J. Xu, S. Lin, X. Wen, E. M. Nichols, K. Jeong and J. A. Reimer, *J. Am. Chem. Soc.*, 2016, **138**, 8120–8125.
- 12 A. S. Hall, Y. Yoon, A. Wuttig and Y. Surendranath, *J. Am. Chem. Soc.*, 2015, **137**, 14834–14837.
- 13 M. Liu, Y. Pang, B. Zhang, P. De Luna, O. Voznyy, J. Xu, X. Zheng, C. T. Dinh, F. Fan and C. Cao, *Nature*, 2016, **537**, 382–386.
- 14 Q. Lu and F. Jiao, *Nano Energy*, 2016, **29**, 439–456.



- 15 Q. Lu, J. Rosen, Y. Zhou, G. S. Hutchings, Y. C. Kimmel, J. G. Chen and F. Jiao, *Nat. Commun.*, 2014, **5**, 1–6.
- 16 Z. Sun, T. Ma, H. Tao, Q. Fan and B. Han, *Chem*, 2017, **3**, 560–587.
- 17 M. Aresta, A. Dibenedetto and A. Angelini, *Chem. Rev.*, 2014, **114**, 1709–1742.
- 18 K. P. Kuhl, E. R. Cave, D. N. Abram and T. F. Jaramillo, *Energy Environ. Sci.*, 2012, **5**, 7050–7059.
- 19 A. Vasileff, C. Xu, Y. Jiao, Y. Zheng and S.-Z. Qiao, *Chem*, 2018, **4**, 1809–1831.
- 20 F. Chang, M. Xiao, R. Miao, Y. Liu, M. Ren, Z. Jia, D. Han, Y. Yuan, Z. Bai and L. Yang, *Electrochem. Energy Rev.*, 2022, **5**, 1–35.
- 21 D. Karapinar, C. E. Creissen, J. G. Rivera de la Cruz, M. W. Schreiber and M. Fontecave, *ACS Energy Lett.*, 2021, **6**, 694–706.
- 22 B. Yang, K. Liu, H. Li, C. Liu, J. Fu, H. Li, J. E. Huang, P. Ou, T. Alkayali and C. Cai, *J. Am. Chem. Soc.*, 2022, **144**, 3039–3049.
- 23 Z. Han, D. Han, Z. Chen, J. Gao, G. Jiang, X. Wang, S. Lyu, Y. Guo, C. Geng and L. Yin, *Nat. Commun.*, 2022, **13**, 1–10.
- 24 Y. Jia, F. Li, K. Fan and L. Sun, *Adv. Powder Mater.*, 2022, **1**, 100012.
- 25 B. Zhang, Y. Jiang, M. Gao, T. Ma, W. Sun and H. Pan, *Nano Energy*, 2021, **80**, 105504.
- 26 Y. F. Nishimura, H.-J. Peng, S. Nitopi, M. Bajdich, L. Wang, C. G. Morales-Guio, F. Abild-Pedersen, T. F. Jaramillo and C. Hahn, *ACS Appl. Mater. Interfaces*, 2021, **13**, 52044–52054.
- 27 S. Gao, Y. Lin, X. Jiao, Y. Sun, Q. Luo, W. Zhang, D. Li, J. Yang and Y. Xie, *Nature*, 2016, **529**, 68–71.
- 28 X. Zheng, Y. Ji, J. Tang, J. Wang, B. Liu, H.-G. Steinrück, K. Lim, Y. Li, M. F. Toney and K. Chan, *Nat. Catal.*, 2019, **2**, 55–61.
- 29 H. A. Hansen, C. Shi, A. C. Lausche, A. A. Peterson and J. K. Nørskov, *Phys. Chem. Chem. Phys.*, 2016, **18**, 9194–9201.
- 30 D. Gao, I. T. McCrum, S. Deo, Y.-W. Choi, F. Scholten, W. Wan, J. G. Chen, M. J. Janik and B. Roldan Cuenya, *ACS Catal.*, 2018, **8**, 10012–10020.
- 31 E. L. Clark, C. Hahn, T. F. Jaramillo and A. T. Bell, *J. Am. Chem. Soc.*, 2017, **139**, 15848–15857.
- 32 Y. Li, F. Cui, M. B. Ross, D. Kim, Y. Sun and P. Yang, *Nano Lett.*, 2017, **17**, 1312–1317.
- 33 P. Grosse, D. Gao, F. Scholten, I. Sinev, H. Mistry and B. Roldan Cuenya, *Angew. Chem., Int. Ed.*, 2018, **57**, 6192–6197.
- 34 Z. Weng, Y. Wu, M. Wang, J. Jiang, K. Yang, S. Huo, X.-F. Wang, Q. Ma, G. W. Brudvig and V. S. Batista, *Nat. Commun.*, 2018, **9**, 1–9.
- 35 P. W. Atkins, J. De Paula and P. W. Atkins, *Physical Chemistry*, W.H. Freeman, New York, 2006.
- 36 J. Qiao, Y. Liu and J. Zhang, *Electrochemical reduction of carbon dioxide. Fundamentals and technologies*, CRC Press, 2016.
- 37 P. Basu, *Chapter 5-Gasification Theory and Modeling of Gasifiers' in Biomass Gasification and Pyrolysis*, Academic Press, Boston, 2010.
- 38 H. Hashiba, H. K. Sato, S. Yotsuhashi, K. Fujii, M. Sugiyama and Y. Nakano, *Sustainable Energy Fuels*, 2017, **1**, 1734–1739.
- 39 W. J. Durand, A. A. Peterson, F. Studt, F. Abild-Pedersen and J. K. Nørskov, *Surf. Sci.*, 2011, **605**, 1354–1359.
- 40 B. Khezri, A. C. Fisher and M. Pumera, *J. Mater. Chem. A*, 2017, **5**, 8230–8246.
- 41 A. M. Appel, J. E. Bercaw, A. B. Bocarsly, H. Dobbek, D. L. DuBois, M. Dupuis, J. G. Ferry, E. Fujita, R. Hille and P. J. Kenis, *Chem. Rev.*, 2013, **113**, 6621–6658.
- 42 L. Torrente-Murciano, D. Mattia, M. D. Jones and P. K. Plucinski, *J. CO2 Util.*, 2014, **6**, 34–39.
- 43 J. Wu, P. P. Sharma, B. H. Harris and X.-D. Zhou, *J. Power Sources*, 2014, **258**, 189–194.
- 44 M. A. Tekalgne, H. H. Do, A. Hasani, Q. Van Le, H. W. Jang, S. H. Ahn and S. Y. Kim, *Mater. Today Adv.*, 2020, **5**, 100038.
- 45 F. Calle-Vallejo and M. T. Koper, *Angew. Chem.*, 2013, **125**, 7423–7426.
- 46 J. H. Montoya, C. Shi, K. Chan and J. K. Nørskov, *J. Phys. Chem. Lett.*, 2015, **6**, 2032–2037.
- 47 J. Wu, Y. Huang, W. Ye and Y. Li, *Adv. Sci.*, 2017, **4**, 1700194.
- 48 X. Nie, W. Luo, M. J. Janik and A. Asthagiri, *J. Catal.*, 2014, **312**, 108–122.
- 49 Z. W. Ulissi, M. T. Tang, J. Xiao, X. Liu, D. A. Torelli, M. Karamad, K. Cummins, C. Hahn, N. S. Lewis and T. F. Jaramillo, *ACS Catal.*, 2017, **7**, 6600–6608.
- 50 H. A. Hansen, C. Shi, A. C. Lausche, A. A. Peterson and J. K. Nørskov, *Phys. Chem. Chem. Phys.*, 2016, **18**, 9194–9201.
- 51 M. K. Birhanu, M.-C. Tsai, A. W. Kahsay, C.-T. Chen, T. S. Zeleke, K. B. Ibrahim, C.-J. Huang, W.-N. Su and B.-J. Hwang, *Adv. Mater. Interfaces*, 2018, **5**, 1800919.
- 52 Y. Hori, K. Kikuchi and S. Suzuki, *Chem. Lett.*, 1985, **14**, 1695–1698.
- 53 Y. Hori, I. Takahashi, O. Koga and N. Hoshi, *J. Phys. Chem. B*, 2002, **106**, 15–17.
- 54 S. Nitopi, E. Bertheussen, S. B. Scott, X. Liu, A. K. Engstfeld, S. Horch, B. Seger, I. E. Stephens, K. Chan and C. Hahn, *Chem. Rev.*, 2019, **119**, 7610–7672.
- 55 *Handbook of Deposition Technologies for Films and Coatings*, ed. P. M. Martin, William Andrew Publishing, Boston, 3rd edn, 2010, pp. 1–31.
- 56 M. J. Hampden-Smith and T. T. Kodas, *Chem. Vap. Deposition*, 1995, **1**, 39–48.
- 57 J. E. Crowell, *J. Vac. Sci. Technol., A*, 2003, **21**, S88–S95.
- 58 I. M. Dharmadasa and J. Haigh, *J. Electrochem. Soc.*, 2006, **153**, G47.
- 59 G. V. Govindaraju, G. P. Wheeler, D. Lee and K.-S. Choi, *Chem. Mater.*, 2017, **29**, 355–370.
- 60 T. S. N. S. Narayanan, I.-S. Park and M.-H. Lee, in *Surface Modification of Magnesium and its Alloys for Biomedical Applications*, ed. T. S. N. S. Narayanan, I.-S. Park and M.-H. Lee, Woodhead Publishing, Oxford, 2015, pp. 29–87.
- 61 A. Bagger, W. Ju, A. S. Varela, P. Strasser and J. Rossmeisl, *ChemPhysChem*, 2017, **18**, 3266–3273.
- 62 H. Tabassum, X. Yang, R. Zou and G. Wu, *Chem. Catal.*, 2022, **2**, 1561–1593.



- 63 M. Sankar, N. Dimitratos, P. J. Miedziak, P. P. Wells, C. J. Kiely and G. J. Hutchings, *Chem. Soc. Rev.*, 2012, **41**, 8099–8139.
- 64 A. Wang, X. Y. Liu, C.-Y. Mou and T. Zhang, *J. Catal.*, 2013, **308**, 258–271.
- 65 P. Wang, M. Qiao, Q. Shao, Y. Pi, X. Zhu, Y. Li and X. Huang, *Nat. Commun.*, 2018, **9**, 4933.
- 66 W. Ju, F. Jiang, H. Ma, Z. Pan, Y. Zhao, F. Pagani, D. Rentsch, J. Wang and C. Battaglia, *Adv. Energy Mater.*, 2019, **9**, 1901514.
- 67 X. Jiang, X. Wang, Z. Liu, Q. Wang, X. Xiao, H. Pan, M. Li, J. Wang, Y. Shao, Z. Peng, Y. Shen and M. Wang, *Appl. Catal., B*, 2019, **259**, 118040.
- 68 K. Ye, A. Cao, J. Shao, G. Wang, R. Si, N. Ta, J. Xiao and G. Wang, *Sci. Bull.*, 2020, **65**, 711–719.
- 69 W. J. Dong, J. W. Lim, D. M. Hong, J. Y. Park, W. S. Cho, S. Baek, C. J. Yoo, W. Kim and J.-L. Lee, *ACS Appl. Energy Mater.*, 2020, **3**, 10568–10577.
- 70 H. Hu, Y. Wang, N. Du, Y. Sun, Y. Tang, Q. Hu, P. Wan, L. Dai, A. C. Fisher and X. J. Yang, *ChemElectroChem*, 2018, **5**, 3854–3858.
- 71 S. Sarfraz, A. T. Garcia-Esparza, A. Jedidi, L. Cavallo and K. Takanabe, *ACS Catal.*, 2016, **6**, 2842–2851.
- 72 Q. Li, J. Fu, W. Zhu, Z. Chen, B. Shen, L. Wu, Z. Xi, T. Wang, G. Lu and J. Zhu, *J. Am. Chem. Soc.*, 2017, **139**, 4290–4293.
- 73 Q. Li, M. Li, S. Zhang, X. Liu, X. Zhu, Q. Ge and H. Wang, *Catalysts*, 2019, **9**, 476.
- 74 M. Zhang, Z. Zhang, Z. Zhao, H. Huang, D. H. Anjum, D. Wang, J. He and K.-W. Huang, *ACS Catal.*, 2021, **11**, 11103–11108.
- 75 W. Luo, W. Xie, R. Mutschler, E. Oveisi, G. L. De Gregorio, R. Buonsanti and A. Züttel, *ACS Catal.*, 2018, **8**, 6571–6581.
- 76 W. Zhang, X. Wen, S. Yang, Y. Berta and Z. L. Wang, *Adv. Mater.*, 2003, **15**, 822–825.
- 77 S. Rasul, D. H. Anjum, A. Jedidi, Y. Minenkov, L. Cavallo and K. Takanabe, *Angew. Chem., Int. Ed.*, 2015, **54**, 2146–2150.
- 78 H. Conrad, G. Ertl and E. E. Latta, *Surf. Sci.*, 1974, **41**, 435–446.
- 79 L. L. Jewell and B. H. Davis, *Appl. Catal., A*, 2006, **310**, 1–15.
- 80 G. Kyriakou, M. B. Boucher, A. D. Jewell, E. A. Lewis, T. J. Lawton, A. E. Baber, H. L. Tierney, M. Flytzani-Stephanopoulos and E. C. H. Sykes, *Science*, 2012, **335**, 1209–1212.
- 81 S. Bai, Q. Shao, P. Wang, Q. Dai, X. Wang and X. Huang, *J. Am. Chem. Soc.*, 2017, **139**, 6827–6830.
- 82 A. A. Peterson and J. K. Nørskov, *J. Phys. Chem. Lett.*, 2012, **3**, 251–258.
- 83 Y. Mun, S. Lee, A. Cho, S. Kim, J. W. Han and J. Lee, *Appl. Catal., B*, 2019, **246**, 82–88.
- 84 T. Adit Maark and B. R. K. Nanda, *J. Phys. Chem. C*, 2016, **120**, 8781–8789.
- 85 J.-F. Xie, J.-J. Chen, Y.-X. Huang, X. Zhang, W.-K. Wang, G.-X. Huang and H.-Q. Yu, *Appl. Catal., B*, 2020, **270**, 118864.
- 86 J. Qiao, Y. Liu, F. Hong and J. Zhang, *Chem. Soc. Rev.*, 2014, **43**, 631–675.
- 87 A. A. Peterson, F. Abild-Pedersen, F. Studt, J. Rossmeisl and J. K. Nørskov, *Energy Environ. Sci.*, 2010, **3**, 1311–1315.
- 88 H.-P. Yang, S. Qin, Y.-N. Yue, L. Liu, H. Wang and J.-X. Lu, *Catal. Sci. Technol.*, 2016, **6**, 6490–6494.
- 89 E. Barton Cole, P. S. Lakkaraju, D. M. Rampulla, A. J. Morris, E. Abelev and A. B. Bocarsly, *J. Am. Chem. Soc.*, 2010, **132**, 11539–11551.
- 90 W. J. Wang, S. Hwang, T. Kim, S. Ha and L. Scudiero, *Electrochim. Acta*, 2021, **387**, 138531.
- 91 D. Chen, Q. Yao, P. Cui, H. Liu, J. Xie and J. Yang, *ACS Appl. Energy Mater.*, 2018, **1**, 883–890.
- 92 R. Feng, Q. Zhu, M. Chu, S. Jia, J. Zhai, H. Wu, P. Wu and B. Han, *Green Chem.*, 2020, **22**, 7560–7565.
- 93 S. Jia, Q. Zhu, H. Wu, M. Chu, S. Han, R. Feng, J. Tu, J. Zhai and B. Han, *Chin. J. Catal.*, 2020, **41**, 1091–1098.
- 94 O. A. Baturina, Q. Lu, M. A. Padilla, L. Xin, W. Li, A. Serov, K. Artyushkova, P. Atanassov, F. Xu and A. Epshteyn, *ACS Catal.*, 2014, **4**, 3682–3695.
- 95 L. Hou, J. Han, C. Wang, Y. Zhang, Y. Wang, Z. Bai, Y. Gu, Y. Gao and X. Yan, *Inorg. Chem. Front.*, 2020, **7**, 2097–2106.
- 96 Y. Chen, Z. Fan, J. Wang, C. Ling, W. Niu, Z. Huang, G. Liu, B. Chen, Z. Lai and X. Liu, *J. Am. Chem. Soc.*, 2020, **142**, 12760–12766.
- 97 S. Ma, M. Sadakiyo, M. Heima, R. Luo, R. T. Haasch, J. I. Gold, M. Yamauchi and P. J. A. Kenis, *J. Am. Chem. Soc.*, 2017, **139**, 47–50.
- 98 S. Zhang, P. Kang, M. Bakir, A. M. Lapides, C. J. Dares and T. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2015, **112**, 15809–15814.
- 99 C. S. Chen, J. H. Wan and B. S. Yeo, *J. Phys. Chem. C*, 2015, **119**, 26875–26882.
- 100 L. Zhu, Y. Lin, K. Liu, E. Cortés, H. Li, J. Hu, A. Yamaguchi, X. Liu, M. Miyauchi and J. Fu, *Chin. J. Catal.*, 2021, **42**, 1500–1508.
- 101 Y.-A. Lai, Y.-C. Chu, C.-J. Chang, K.-H. Chen, Y.-C. Hsiao, C.-C. Chang, M.-Y. Liao and H. M. Chen, *Adv. Energy Sustain. Res.*, 2022, 2200075.
- 102 X.-Q. Li, G.-Y. Duan, X.-X. Yang, L.-J. Han and B.-H. Xu, *Fundam. Res.*, 2022, DOI: [10.1016/j.fmre.2021.12.009](https://doi.org/10.1016/j.fmre.2021.12.009).
- 103 H. Shen, Y. Wang, T. Chakraborty, G. Zhou, C. Wang, X. Fu, Y. Wang, J. Zhang, C. Li and F. Xu, *ACS Catal.*, 2022, **12**, 5275–5283.
- 104 Z. Li, R. M. Yadav, L. Sun, T. Zhang, J. Zhang, P. M. Ajayan and J. Wu, *Appl. Catal., A*, 2020, **606**, 117829.
- 105 F. Quan, D. Zhong, H. Song, F. Jia and L. Zhang, *J. Mater. Chem. A*, 2015, **3**, 16409–16413.
- 106 B. Qin, Y. Li, H. Fu, H. Wang, S. Chen, Z. Liu and F. Peng, *ACS Appl. Mater. Interfaces*, 2018, **10**, 20530–20539.



## Review

- 107 J. Rosen, G. S. Hutchings, Q. Lu, R. V. Forest, A. Moore and F. Jiao, *ACS Catal.*, 2015, **5**, 4586–4591.
- 108 D. Ren, B. S.-H. Ang and B. S. Yeo, *ACS Catal.*, 2016, **6**, 8239–8247.
- 109 G. Keerthiga and R. Chetty, *J. Electrochem. Soc.*, 2017, **164**, H164.
- 110 X. Su, Y. Sun, L. Jin, L. Zhang, Y. Yang, P. Kerns, B. Liu, S. Li and J. He, *Appl. Catal., B*, 2020, **269**, 118800.
- 111 D. Ren, J. Gao, L. Pan, Z. Wang, J. Luo, S. M. Zakeeruddin, A. Hagfeldt and M. Grätzel, *Angew. Chem., Int. Ed.*, 2019, **58**, 15036–15040.
- 112 S. Dongare, N. Singh, H. Bhunia and P. K. Bajpai, *Electrochim. Acta*, 2021, **392**, 138988.
- 113 T. T. Hoang, S. Verma, S. Ma, T. T. Fister, J. Timoshenko, A. I. Frenkel, P. J. Kenis and A. A. Gewirth, *J. Am. Chem. Soc.*, 2018, **140**, 5791–5797.
- 114 J. Huang, M. Mensi, E. Oveisi, V. Mantella and R. Buonsanti, *J. Am. Chem. Soc.*, 2019, **141**, 2490–2499.
- 115 J. Wang, Z. Li, C. Dong, Y. Feng, J. Yang, H. Liu and X. Du, *ACS Appl. Mater. Interfaces*, 2019, **11**, 2763–2767.
- 116 Y. Wang, C. Niu and Y. Zhu, *Nanomaterials*, 2019, **9**, 173.
- 117 Y. Wang, D. Wang, C. J. Dares, S. L. Marquard, M. V. Sheridan and T. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 278–283.
- 118 D. Higgins, A. T. Landers, Y. Ji, S. Nitopi, C. G. Morales-Guio, L. Wang, K. Chan, C. Hahn and T. F. Jaramillo, *ACS Energy Lett.*, 2018, **3**, 2947–2955.
- 119 D. Ren, J. Fong and B. S. Yeo, *Nat. Commun.*, 2018, **9**, 925.
- 120 A. Katoh, H. Uchida, M. Shibata and M. Watanabe, *J. Electrochem. Soc.*, 1994, **141**, 2054.
- 121 J. Choi, M. J. Kim, S. H. Ahn, I. Choi, J. H. Jang, Y. S. Ham, J. J. Kim and S.-K. Kim, *Chem. Eng. J.*, 2016, **299**, 37–44.
- 122 Z. Chang, S. Huo, W. Zhang, J. Fang and H. Wang, *J. Phys. Chem. C*, 2017, **121**, 11368–11379.
- 123 M. Watanabe, M. Shibata, A. Kato, M. Azuma and T. Sakata, *J. Electrochem. Soc.*, 1991, **138**, 3382.
- 124 Z. Yin, D. Gao, S. Yao, B. Zhao, F. Cai, L. Lin, P. Tang, P. Zhai, G. Wang and D. Ma, *Nano Energy*, 2016, **27**, 35–43.
- 125 D. Kim, C. Xie, N. Becknell, Y. Yu, M. Karamad, K. Chan, E. J. Crumlin, J. K. Nørskov and P. Yang, *J. Am. Chem. Soc.*, 2017, **139**, 8329–8336.
- 126 K. Chen, X. Zhang, T. Williams, L. Bourgeois and D. R. MacFarlane, *Electrochim. Acta*, 2017, **239**, 84–89.
- 127 S. Sultan, H. Lee, S. Park, M. M. Kim, A. Yoon, H. Choi, T.-H. Kong, Y.-J. Koe, H.-S. Oh and Z. Lee, *Energy Environ. Sci.*, 2022, **15**, 2397–2409.

