

Organic & Biomolecular Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

A PEPTIDE TOPOLOGICAL TEMPLATE FOR THE DISPERSION OF [60]FULLERENE IN WATER

S. Bartocci, D. Mazzier, A. Moretto, M. Mba*

Department of Chemical Sciences, University of Padova, via Marzolo 1, 35135, Padova (Italy).

e-mail: miriam.mba@unipd.it

Abstract

Solubilization of [60]fullerene in water is a major challenge for biological and medical applications. To this purpose in this communication we describe for the first time a new dispersing system based on a peptide topological template. The presence of two carbobenzyloxy groups on the peptide side chains allows π - π interactions with [60]fullerene leading to the formation of stable supramolecular nanocomposites by means of mechanochemical methods. In particular, by high speed vibration milling colloidal dispersions (mean particle diameter 63 nm) containing up to 1.3 mg/mL of [60]fullerene were obtained. Its presence in water was verified through UV-Vis and MALDI-TOF measurements, while its concentration was determined by thermogravimetric analysis.

After the discovery of [60]fullerene,¹ the third allotropic form of carbon, many scientists were attracted by this fascinating spherical cage and the challenge to study and exploit its properties in different scientific areas. Pristine fullerene is an excellent electron acceptor extensively used in organic solar cells.^{2, 3} On the other hand, it plays also an important role in biological and medical applications as enzyme inhibitor, antiviral agent or for DNA cleavage and photodynamic therapy.⁴⁻⁸ However, the use of the buckyball in these fields has been hampered by its poor solubility in water. On the base of this, there have been several attempts to overcome the natural hydrophobicity of [60]fullerene. One of the possible strategies is the dispersion of [60]fullerene in the form of aggregates (nC_{60}). It has been suggested that colloidal dispersions of nC_{60} in water may be the main form of fullerene in aquatic systems,⁹ therefore, toxicity and biological studies using these dispersions are of high importance. Stable colloidal dispersions of [60]fullerene can be obtained by the so-called solvent exchange method in which [60]fullerene is transferred from THF, acetone or toluene into water.¹⁰⁻¹² Only in one report, THF traces could be eliminated by gamma irradiation.¹³ These methodologies led in general to traces of these highly toxic organic solvents in

the aqueous solution and therefore are not suited for biological or medical applications. Sonication^{14, 15} or stirring in water¹⁶ for long periods of time, weeks or even months, without the addition of any organic solvent have been used, but as in the solvent-exchange method, the concentration of fullerene achieved in the colloidal solution is very low. Covalent functionalization with suitable hydrophilic substituents leads to water-soluble fullerene derivatives,¹⁷ but disruption of the π -system may modify its properties and consequently the biological activity. For this reason, non-covalent approaches have been attempted. In particular, complexation of [60]fullerene with a host molecule, such as γ -cyclodextrin, calixarene, cucurbituril and so on, has been proposed for molecular solutions of [60]fullerene.^{18, 19} However, these hosts are expensive and difficult to synthesize and, in the other hand, for biological and medical applications the use of biocompatible molecules is highly desirable. Stable dispersions of [60]fullerene have been obtained using biocompatible molecules to stabilize the aggregates, as carbohydrates²⁰ and proteins.²¹ In this context, we have recently reported a lysine-based hydrogelator able to solubilize [60]fullerene, multi-walled carbon nanotubes (MWCNTs) and graphene in water via a mechanochemical approach.²² In this hydrogelator the presence of two 9-fluorenylmethoxycarbonyl (Fmoc) groups ensured π - π interactions with [60]fullerene and two free amines guaranteed the solubility in water. Stable colloidal dispersions of [60]fullerene aggregates were obtained at a concentration of 0.8 mg/mL.

In this communication we report the dispersion of [60]fullerene in water through non-covalent functionalization with a cyclic decapeptide **1** (Figure 1a). Peptide **1** has been inspired by the peptide topological templates described by Mutter.^{23, 24} These templates present two distinct spatially independent functional domains: four side chains are pointing outwards one face of the cyclic molecule and other two are pointing to the opposite face. In our case, one domain will be used to interact with [60]fullerene, the other to control solubility.

Decapeptide **1** contains six lysines (K) and two Pro-Gly (P-G) β -turns arranged in a β sheet secondary structure (Figure 1a). The amino group of the side chain is in its free form in the case of the four lysines of one spatial domain, while it is carbobenzyloxy-protected in the case of the two lysines belonging to the spatial domain of the opposite face. The four free amino groups act as hydrophilic functionalities and the two carbobenzyloxy groups (Z) as functional ligands for π - π interactions with [60]fullerene.

Standard Fmoc mediated solid phase peptide synthesis (SPPS) protocols were used to synthesize the linear decapeptide **2**, that was then cyclized using

(benzotriazol-1-yloxy)tripyrrolidinophosphonium hexafluorophosphate (pyBOP) as coupling reagent (for details see SI). Finally, treatment with trifluoroacetic acid (TFA) removed the *tert*-butyloxycarbonyl (Boc) groups to give **1**. The structure of **1** was confirmed by NMR, IR and MS (see SI). Peptide **1** proved to be soluble in water at acidic and neutral pH up to 20 mg/mL. At this concentration, when NaOH 1M was added, a transparent stable hydrogel was obtained. Transmission electron microscopy (TEM) images of the xerogel showed the formation of stripes up to 4 μm long (Figure 1b). We can suppose that in these stripes the molecules are arranged in a way in which the hydrophobic part of the molecule is buried inside the supramolecular structures, whereas the hydrophilic part should be in contact with the solvent.

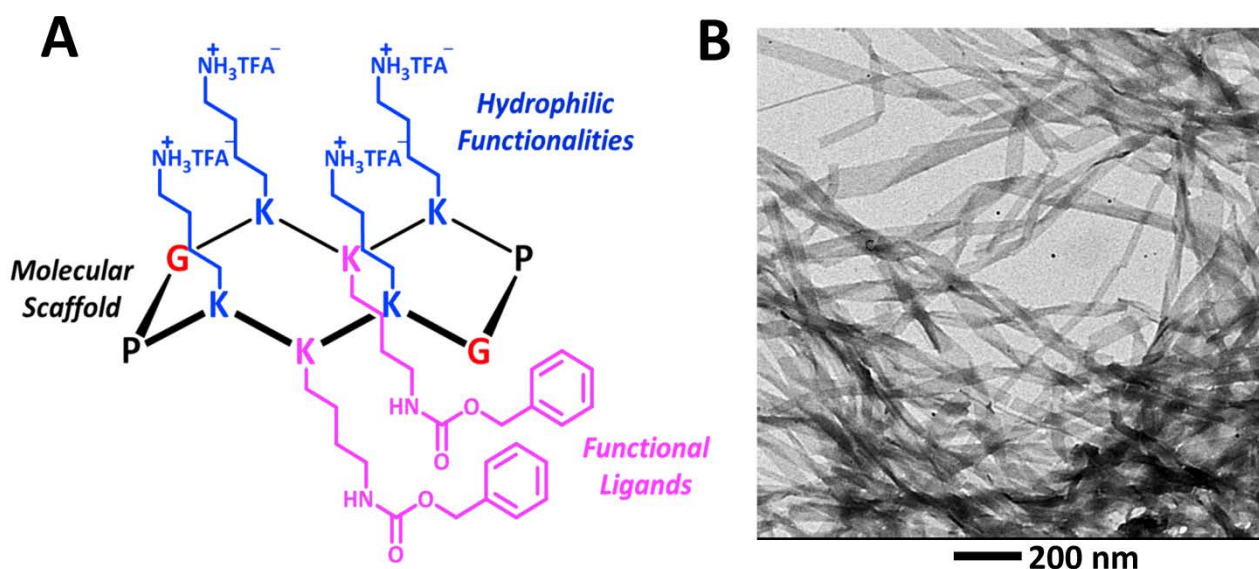


Figure 1. a) Structure of **1**. b) TEM images (uranyl stained) of the xerogel obtained from **1**.

With the aim to compare different methodologies, the **1**/ C_{60} nanocomposites were obtained by sonication in water, manual grinding and high speed vibration milling (HSVM). Sonication in water has been traditionally used to obtain inclusion complexes of [60]fullerene with different hosts,²⁵ whereas the mechanochemical methodologies are less usual but had demonstrated their utility in covalent and non-covalent functionalization of the highly insoluble carbon nanostructures.²⁶ We applied a high-power sonication tip for 1 hour on a suspension of [60]fullerene and **1** in mmQ water (0.3 mL/ mg C_{60}). The resulting mixture was then centrifuged first at 4000 rpm to remove insoluble parts and then at 14000 rpm to eliminate larger aggregates. Finally, it was filtered through a 45 μm membrane. In the manual grinding methodology the two solids were grinded in

an agate mortar for 20 min, whereas in the case of the HSVM the solids were placed in a stainless-steel milling cup with five stainless-steel mixing balls and a frequency of 30 Hz for 10 minutes was used. The resulting solids were suspended in mmQ water (0.3 mL/ mg C₆₀), stirred 1h at room temperature and then treated as described above. In a first set of experiments a 1/C₆₀ ratio = 2:1 was used, but most of the [60]fullerene remained insoluble. However, using a 4:1 ratio colored solutions were obtained, indicating the presence of fullerene in water. We obtained a reddish-amber solution for the HSVM sample, gold-amber for the manual grinding one and pale yellow for that obtained using sonication (Figure 2a). The difference in the color intensity indicates qualitatively that the sample obtained from HSVM displays the higher concentration of [60]fullerene.

The presence of fullerene in the solutions was further confirmed by UV-Vis spectroscopy. The absorption spectrum of all the samples clearly shows three new absorption maxima at 262, 341 and 434 nm plus a weak absorption at 622 nm (Figure 2a). This profile resembles those reported previously for fullerene aggregates (nC₆₀) dispersed in water and indicates that the fullerene cage has remained chemically intact during the process.^{27, 28} MALDI-TOF experiments showed only the peak of [60]fullerene at m/z 720 (Figure 2b), further confirming that no chemical modifications have taken place during the process.

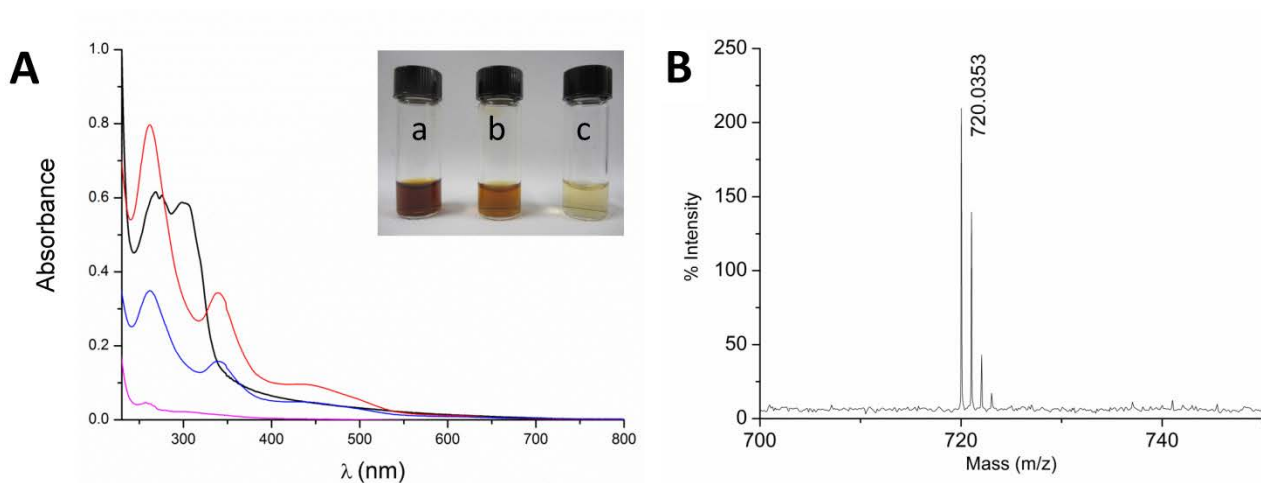


Figure 2. a) UV-Vis spectra of aqueous solutions of **1** (black) and **1/C**₆₀ nanocomposites obtained by HSVM (red), manual grinding (blue) and sonication (pink). Inset: picture of the solutions obtained by HSVM (a), manual grinding (b) and sonication (c). b) MALDI-TOF mass spectrum of the solution obtained by HSVM

The concentration of [60]fullerene in the solutions was determined by thermogravimetric analysis (TGA) from the relative lyophilized samples. In all cases three main weight losses at 186, 268 and a last one from 545 to 700°C (TGA analysis under nitrogen) were observed: the first two losses are attributed to the cyclic decapeptide while the third one includes also a weight loss due to degradation of fullerene (Figure 3 and Figures in the SI). Comparing with the TGA data of **1** alone, the results indicate that we were able to solubilize 1.3, 0.7 and 0.1 mg/mL of C₆₀ by HSVM, manual grinding and sonication procedure respectively. Therefore HSVM with peptide **1** allows to obtain the higher concentration of [60]fullerene and our procedure is far superior to other methods reported to date in literature for the dispersion of [60]fullerene in form of aggregates.^{10-12, 20, 21}

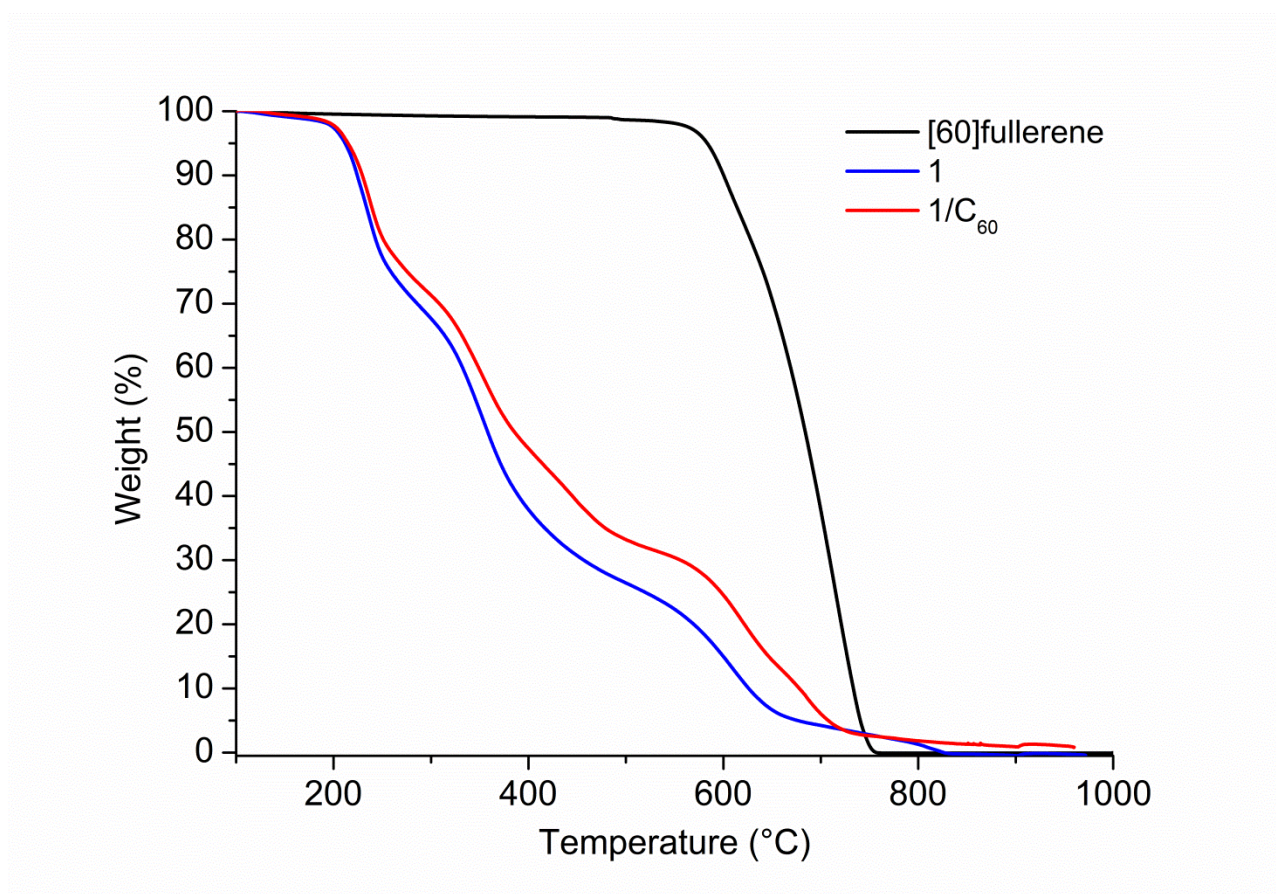


Figure 3. TGA analysis (under nitrogen atmosphere) of [60]fullerene, **1** and the **1/C₆₀** solution obtained by HSVM.

The non-covalent interaction between decapeptide **1** and [60]fullerene was confirmed by circular dichroism (CD) spectroscopy. In the CD spectra weak Cotton effects could be observed in the absorption region of fullerene indicating a transfer of chirality from the chiral decapeptide to the “achiral” fullerene due to a close interaction (Figure 4). Most likely the non-covalent interaction

between **1** and [60]fullerene consists mainly in π - π interactions between the π -cloud of fullerene and the aromatic Z group of the peptide.

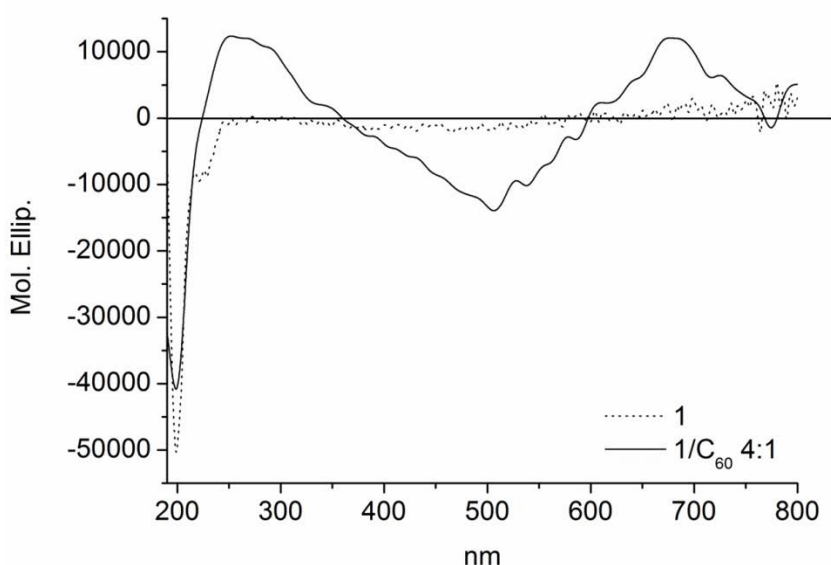


Figure 4. CD spectra of aqueous solutions of peptide **1** (dotted line) and **1/C₆₀** obtained by HSVM (solid line).

Particle size of nC₆₀ aggregates has been proved to affect strongly the biological properties of its dispersions.^{16, 29} For this reason we investigated the particle size of the dispersions obtained by HSVM by dynamic light scattering (DLS) a well-established technique used to determine the size of proteins, micelles and nanoparticles in solution. In Figure 5 we report our results on the size distribution of the solution obtained by HSVM before and after centrifugation at high speed (14000 rpm, 5 min). An opaque solution was obtained upon centrifugation at 4000 rpm that showed two different populations of nanoparticles in the intensity distribution (Figure 5A). An additional centrifugation at 14000 rpm removed the larger aggregates leading to a transparent solution that showed a single population of aggregates with a mean particle size of 63 nm that is smaller than those reported in literature for dispersions of C₆₀ in water obtained by solvent-exchange methods.³⁰ Further centrifugation cycles did not cause any changes in the DLS measurements. Transmission electron microscopy (TEM) showed the presence of aggregates of spherical shape with diameters ranging from 20 to 60 nm (Figure 6), confirming DLS measurements.

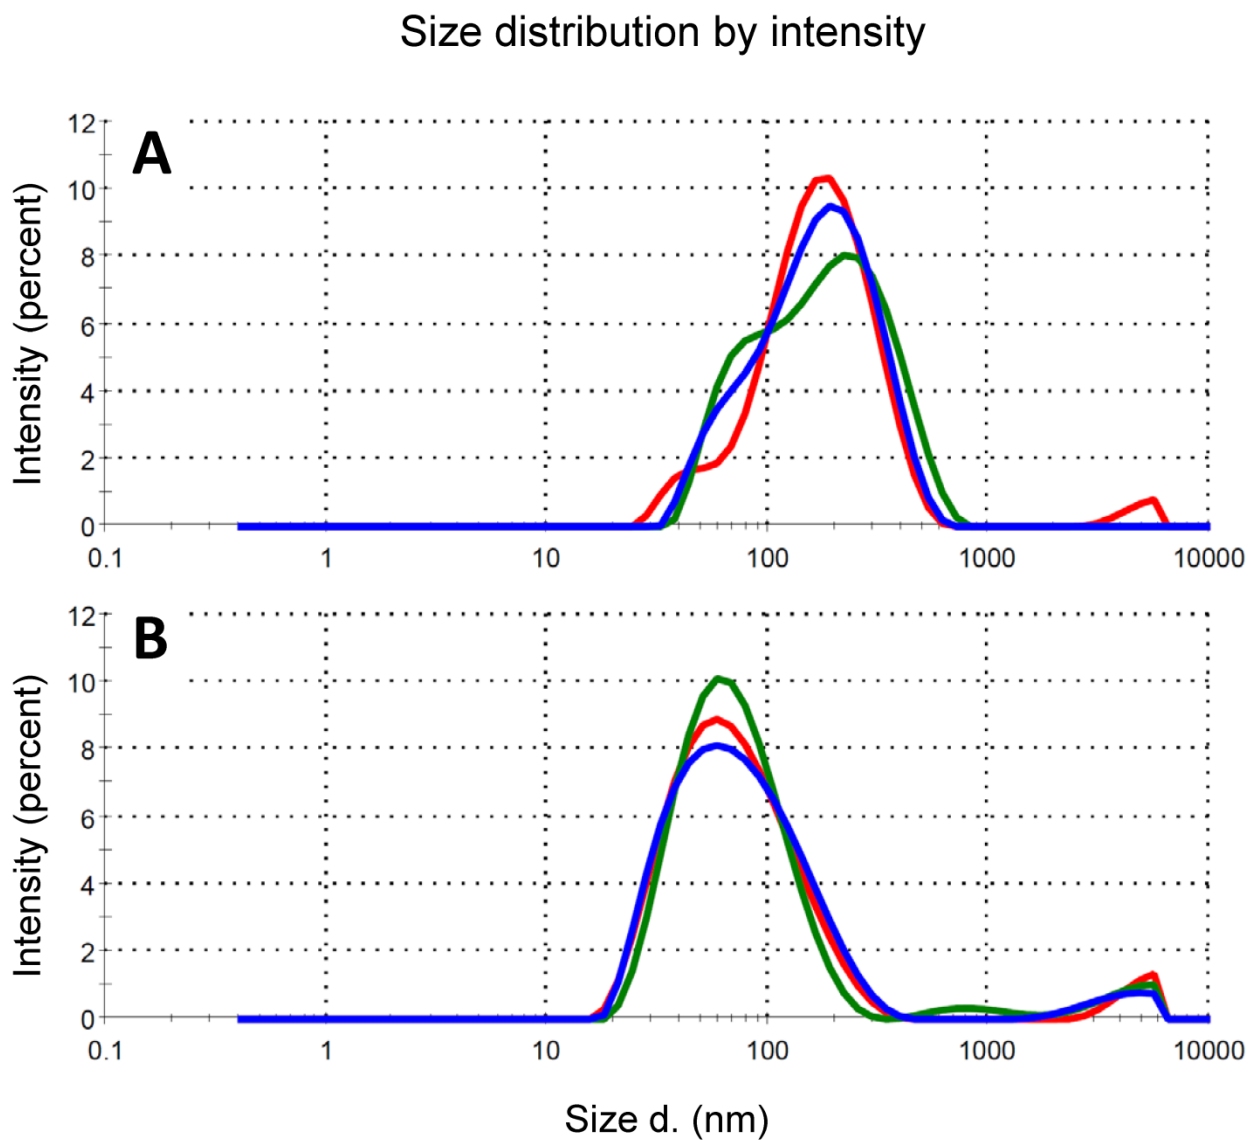


Figure 5. DLS of the aqueous solutions of 1/C₆₀ nanocomposites obtained by HSV: a) upon centrifugation at 4000 rpm, b) upon centrifugation at 14000 rpm.

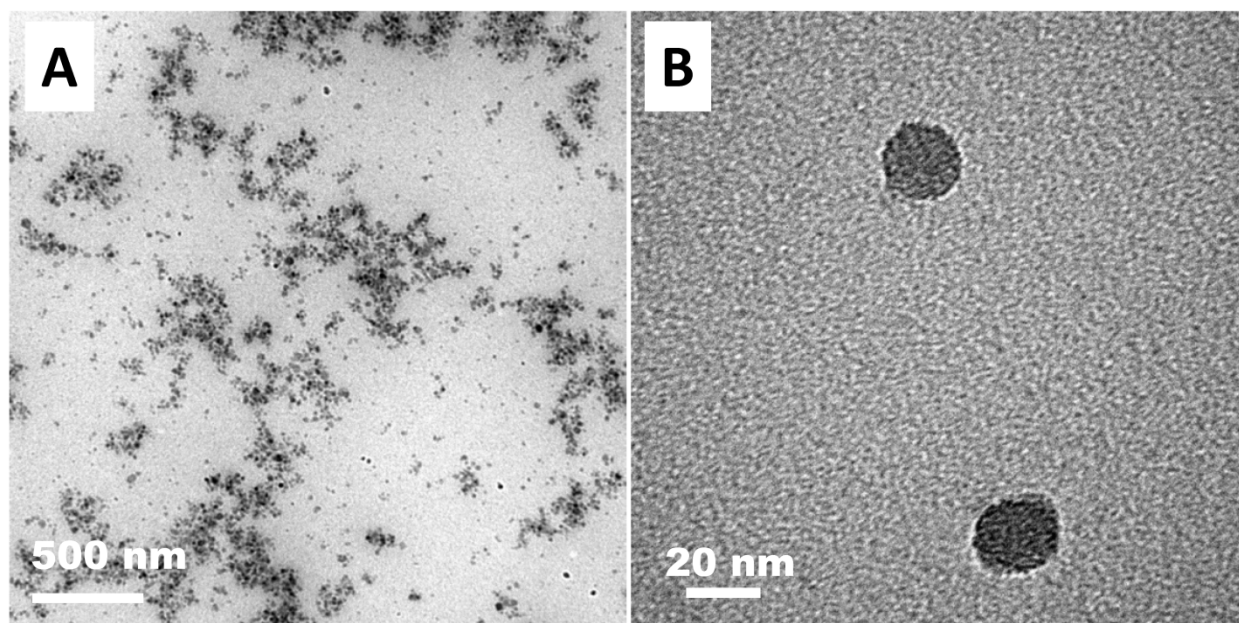


Figure 6. TEM images of the colloidal dispersion of **1**/ C_{60} obtained by HSVM.

Recently, different authors have shown that in colloidal dispersions of nC_{60} the spectral properties of the dispersions depend on the particle size of the nC_{60} aggregates.^{15, 28, 31} In particular, the position of the band found at 330-360 nm is a linear function of the hydrodynamic diameter (Z_{ave}). From the different equations reported in literature, Equation 1 obtained by Deguchi et al. for colloidal dispersions of nC_{60} with particle size between 30 and 200 nm stabilized by surfactants¹⁵ is the most appropriate, since the system used by the authors is the one resembling better the conditions presented in this paper.

$$\lambda_{max}(360) = (0.065 \pm 0.009) Z_{ave} + (337.1 \pm 1.4) \quad (1)$$

Introducing in this Equation the mean particle size value observed by DLS (63 nm) a predicted value of 341.1 nm is obtained for $\lambda_{max}(360)$, which is in complete agreement with the experimental value found by UV-Vis spectroscopy (341 nm).

The zeta potential measured by DLS for the colloidal dispersion obtained by HSVM had positive value of 24.7 mV, which demonstrates the formation of positively charged surfaces around the nC_{60} aggregates by peptide **1**.

Another important factor for biological and medical applications is the stability of the dispersion of [60]fullerene aggregates. The high value of zeta potential is the first indication of the high stability of the dispersion, as at large Z potential value the electrostatic repulsions should prevent further

aggregation of the nC_{60} nanoparticles. We were delighted to find that solutions were stable for months (at least two months) on storage at room temperature and no precipitation of any solids was observed. The mean particle size of the aged solutions found by DLS measurements was similar to the one encountered for the freshly prepared samples (see SI), so no aggregation of the nanoparticles occurred upon time. Moreover, the solutions could be lyophilized and the resulting powders could be stored at room temperature for weeks and then re-dissolved in water without aggregation or precipitation. Dispersions were stable in physiological solution, no precipitation was observed in the presence of 1% NaCl even after 24h of the addition of salt. Due to the presence of four charged ammonium groups we expected the solutions to be sensitive to pH changes. The dispersions were stable at neutral and acidic pH. In contrast, addition of base leads to precipitation and not to hydrogel formation as observed for peptide **1** alone. This is probably due to a concentration lower than 20 mg/mL of peptide in the **1**/ C_{60} solutions.

In conclusion, we have synthesized a cyclic decapeptide **1** and, using high speed vibration milling, we were able to obtain efficiently water soluble **1**/ C_{60} nanocomposites without the aid of organic solvents. Highly homogeneous dispersions of [60]fullerene aggregates in water with concentration up to 1.3 mg/mL were achieved when a **1**/ C_{60} ratio 4:1 was used. We are currently working on the use of the colloidal dispersions of [60]fullerene obtained in this work in biological and medical applications, as appropriate functionalization of the topological template could allow the introduction of recognition sites or any other functionality of interest.

Electronic supplementary information

Electronic supplementary information (ESI) available: synthesis and full characterization of **1** and **2**. TGA analysis, MALDI-TOF mass spectra and DLS measurements.

Acknowledgements

The authors are grateful to Dr. F. Caicci (U. Padova) for TEM data recording. The University of Padova (PRAT CPDA114475, PRAT CPDA119117,) and MIUR (FIRB project NANOSOLAR RBAP11C58Y) are acknowledged for financial support. S.B. acknowledges the University of Padova for a postdoctoral grant (assegno di ricerca junior CPDR131937).

1. H. W. Kroto, J. R. Heath, S. C. O'Brien, R. F. Curl and R. E. Smalley, *Nature*, 1985, **318**, 162-163.
2. B. C. Thompson and J. M. J. Fréchet, *Angew. Chem. Int. Ed.*, 2008, **47**, 58-77.
3. P. Hudhomme and J. Cousseau, in *Fullerenes: Principles and Applications (2)*, The Royal Society of Chemistry, 2012, pp. 416-461.
4. R. Bakry, R. M. Vallant, M. Najam-Ul-Haq, M. Rainer, Z. Szabo, C. W. Huck and G. K. Bonn, *Int. J. Nanomed.*, 2007, **2**, 639-649.
5. A. Bianco and T. Da Ros, in *Fullerenes: Principles and Applications (2)*, The Royal Society of Chemistry, 2012, pp. 507-545.
6. R. Partha and J. L. Conyers, *Int. J. Nanomed.*, 2009, **4**, 261-275.
7. A. W. Jensen, S. R. Wilson and D. I. Schuster, *Bioorg. Med. Chem.*, 1996, **4**, 767-779.
8. S. Bosi, T. Da Ros, G. Spalluto and M. Prato, *Eur. J. Med. Chem.*, 2003, **38**, 913-923.
9. L. K. Duncan, J. R. Jinschek and P. J. Vikesland, *Environ. Sci. Technol.*, 2007, **41**, 173-178.
10. W. A. Scrivens, J. M. Tour, K. E. Creek and L. Pirisi, *J. Am. Chem. Soc.*, 1994, **116**, 4517-4518.
11. G. V. Andrievsky, M. V. Kosevich, O. M. Vovk, V. S. Shelkovsky and L. A. Vashchenko, *J. Chem. Soc., Chem. Commun.*, 1995, 1281-1282.
12. S. Deguchi, R. G. Alargova and K. Tsujii, *Langmuir*, 2001, **17**, 6013-6017.
13. A. Isakovic, Z. Markovic, N. Nikolic, B. Todorovic-Markovic, S. Vranjes-Djuric, L. Harhaji, N. Raicevic, N. Romcevic, D. Vasiljevic-Radovic, M. Dramicanin, V. Trajkovic, *Biomaterials*, 2006, **27**, 5049-5058
14. T. Benn, B. G. Pycke, P. Herckes, P. Westerhoff and R. Halden, *Anal. Bioanal. Chem.*, 2011, **399**, 1631-1639.
15. S. Deguchi, S.-a. Mukai, T. Yamazaki, M. Tsudome and K. Horikoshi, *J. Phys. Chem. C*, 2009, **114**, 849-856.
16. D. Y. Lyon, L. K. Adams, J. C. Falkner and P. J. J. Alvarez, *Environ. Sci. Technol.*, 2006, **40**, 4360-4366.
17. T. Da Ros, M. Prato, F. Novello, M. Maggini and E. Banfi, *J. Org. Chem.*, 1996, **61**, 9070-9072.
18. A. Ikeda, A. Hirata, M. Ishikawa, J.-i. Kikuchi, S. Mieda and W. Shinoda, *Organic & Biomolecular Chemistry*, 2013, **11**, 7843-7851.
19. K. Nobusawa, D. Payra and M. Naito, *Chem. Commun.*, 2014, **50**, 8339-8342.
20. V. I. Bhoi, S. Kumar and C. N. Murthy, *Carbohydr. Res.*, 2012, **359**, 120-127.
21. H. Wu, L. Lin, P. Wang, S. Jiang, Z. Dai and X. Zou, *Chem. Commun.*, 2011, **47**, 10659-10661.
22. M. Mba, A. I. Jiménez and A. Moretto, *Chem. Eur. J.*, 2014, **20**, 3888-3893.
23. S. Peluso, T. Ruckle, C. Lehmann, M. Mutter, C. Peggion and M. Crisma, *Chembiochem*, 2001, **2**, 432-437.
24. G. V. Nikiforovich, M. Mutter and C. Lehmann, *Biopolymers*, 1999, **50**, 361-372.
25. P. Hammershøj, P. H. H. Bomans, R. Lakshminarayanan, J. Fock, S. H. Jensen, T. S. Jespersen, T. Brock-Nannestad, T. Hassenkam, J. Nygård, N. A. J. M. Sommerdijk, K. Kilså, T. Bjørnholm and J. B. Christensen, *Chem. Eur. J.*, 2012, **18**, 8716-8723.
26. S.-E. Zhu, F. Li and G.-W. Wang, *Chem. Soc. Rev.*, 2013, **42**, 7535-7570.
27. P. Scharff, K. Risch, L. Carta-Abelmann, I. M. Dmytruk, M. M. Bilyi, O. A. Golub, A. V. Khavryuchenko, E. V. Buzaneva, V. L. Aksenov, M. V. Avdeev, Y. I. Prylutsky and S. S. Durov, *Carbon*, 2004, **42**, 1203-1206.
28. X. J. Chang and P. J. Vikesland, *Environ. Sci. Technol.*, 2011, **45**, 9967-9974.
29. A. Dhawan, J. S. Taurozzi, A. K. Pandey, W. Shan, S. M. Miller, S. A. Hashsham and V. V. Tarabara, *Environ. Sci. Technol.*, 2006, **40**, 7394-7401.
30. J. A. Brant, J. Labille, J.-Y. Bottero and M. R. Wiesner, *Langmuir*, 2006, **22**, 3878-3885.
31. H. Kato, A. Nakamura, K. Takahashi and S. Kinugasa, *Phys. Chem. Chem. Phys.*, 2009, **11**, 4946-4948.