

Cite this: *J. Mater. Chem. A*, 2024, 12, 11090

A MOF-derived pyrrolic N-stabilized Ni single atom catalyst for selective electrochemical reduction of CO₂ to CO at high current density†

Jin Wook Lim,^{‡a} Dong Heon Choo,^{‡b} Jin Hyuk Cho,^{‡c} Jaehyun Kim,^d Won Seok Cho,^a Odongo Francis Ngome Okello,^a Kisoo Kim,^{id a} Sungwon Lee,^a Junwoo Son,^{id a} Si-Young Choi,^{id a} Jong Kyu Kim,^a Ho Won Jang,^{id *d} Soo Young Kim^{id *c} and Jong-Lam Lee^{id *ab}

Electrochemical reduction of CO₂ to chemical fuels with a transition metal-based single atom catalyst (SAC) offers a promising strategy to reduce CO₂ with high catalytic selectivity. To date, the study of atomically dispersed SACs has been mainly conducted by using a conventional H-type cell system with limited solubility of CO₂ in aqueous electrolytes, resulting in large overpotentials and low current density. Here, we reported a pyrrolic N-stabilized Ni SAC with low-coordinated Ni–N_x sites by thermal activation of Ni ZIF-8, which was tested in a 3-compartment microfluidic flow cell system at the industrial level. When the pyrolysis temperature increased from 800 °C (Ni SAC-800) to 1000 °C (Ni SAC-1000), the content ratio of pyrrolic N/pyridinic N increased from 0.37 to 1.01 as well as the coordination number of Ni in Ni–N_x sites decreased from 3.14 to 2.63. Theoretical calculations revealed that the synergistic effect between the high content ratio of pyrrolic N and low-coordinated Ni can decrease the energy barrier for the desorption of *CO during the CO₂RR. Therefore, Ni SAC-1000 exhibited superior catalytic performances with high CO selectivity (FE_{CO} = 98.24% at –0.8 V_{RHE}) compared to that of Ni SAC-800 (FE_{CO} = 40.76% at –0.8 V_{RHE}). Moreover, Ni SAC-1000 based on the flow cell system showed a higher current density (~200 mA cm^{–2}) compared to that of the H-type cell system (~20 mA cm^{–2}). As a result, this study experimentally demonstrated that the pyrrolic N-stabilized and low-coordinated Ni SAC-1000 in the microfluidic flow cell reactor provides great chances for scaling up the productivity of the CO₂RR at the industrial level.

Received 20th October 2023
Accepted 25th February 2024

DOI: 10.1039/d3ta06399b

rsc.li/materials-a

Introduction

The conversion of CO₂ to chemical fuels by the electrochemical CO₂ reduction reaction (CO₂RR) with renewable electricity is an effective way to solve global climate changes and achieve carbon recycling in human society.^{1–5} Among the possible chemical fuels of the CO₂RR, carbon monoxide (CO) is one of the most desired products because it was generated by low electron consumption of CO₂ and could be further converted to methanol, hydrocarbons, and petroleum through Fischer–Tropsch

synthesis.⁶ To date, nanostructure-based metal catalysts such as Ag nanowires,^{7,8} 3D hierarchical Cu,^{9,10} and Au nanoneedles¹¹ have been demonstrated to improve the catalytic performances of CO production because they have a large catalytic surface area for the CO₂RR.^{7–16} But, it still suffered from large overpotentials and highly competitive hydrogen evolution reaction (HER) in an aqueous system.^{17,18}

Recently, single atom catalysts (SACs) have emerged as a promising candidate for the CO₂RR because they have atomically dispersed active sites and can easily change the local coordination environments.^{19–22} Especially, a non-noble and earth-abundant Ni-based SAC coordinated in a carbon matrix with neighboring N configurations (Ni–N_x–C structure) has been demonstrated to be highly selective in CO production.^{23–27} Because the Ni–N_x configurations play a role in active sites for the CO₂RR, there were several studies to modulate the coordination structure and local environment of the Ni species.²⁵ For instance, Yan *et al.* suggested that unsaturated Ni–N_x sites effectively strengthen the CO₂ adsorption, leading to an increase in the catalytic selectivity of CO (FE_{CO} = 92% at –1.03 V_{RHE}).²⁸ In addition, low-valent Ni⁺ species anchored on a N-

^aDepartment of Materials Science and Engineering, Pohang University of Science and Technology (POSTECH), Pohang 790-784, Korea. E-mail: jllee@postech.ac.kr^bDivision of Advanced Materials Science, Pohang University of Science and Technology (POSTECH), Pohang 790-784, Korea^cDepartment of Materials Science and Engineering, Korea University, Seoul, Korea. E-mail: sooyoungkim@korea.ac.kr^dDepartment of Materials Science and Engineering, Research Institute of Advanced Materials, Seoul National University, Seoul 08826, Korea. E-mail: hwjang@snu.ac.kr† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ta06399b>

‡ These authors equally contributed to this work.



doped graphene matrix showed high selectivity toward CO production ($FE_{CO} = 94\%$ at $-0.9 V_{RHE}$).²⁹ Pranav *et al.* reported that various nitrogen species bonded with metal, such as graphitic N, pyridinic N, and pyrrolic N, acted as the active sites for the CO₂RR based on density functional theory (DFT) calculations.³⁰ Despite several kinds of research on Ni-based SACs for the CO₂RR, the reason for the enhanced catalytic activities remains unclear due to the complexity of various factors, and more importantly, the role of different types of N configurations in the CO₂RR still remains elusive.

The most effective and easy way to control the N configurations in Ni-based SACs could be pyrolysis treatment at high temperatures. During the pyrolysis process, the Ni and N species react with each other to form various active Ni-N_x sites and make different N configurations depending on the process conditions. Thus, understanding the role of types of N configurations fabricated under different pyrolysis conditions can provide insights into the relationship between the local Ni-N_x structure and catalytic performances, enabling the making of efficient catalysts.

So far, CO current density for previously reported Ni SACs with a Ni-N_x-C structure has been limited because most of them were evaluated in conventional H-type electrochemical cell systems.^{31–35} In a typical H-type cell system, the CO₂ gas was supplied to the catalytic surface through aqueous electrolytes. The current density of CO₂ conversion could be restricted due to the low CO₂ solubility and slow diffusion of CO₂ in aqueous solution, resulting in hardly satisfying the current density of the industrial level ($>100 \text{ mA cm}^{-2}$).³⁶ To scale up the productivity of the CO₂RR at the practical level, a gas diffusion electrode (GDE)-based flow cell system could be employed, where the CO₂ gas was directly supplied to the catalytic surface without containing the aqueous solution. The flow cell system can produce high current density because of the continuous contact between CO₂ and the catalyst as well as the fast diffusion of CO₂ gas. Thus, the microfluidic flow cell system is a promising candidate for enhancing the productivity of the CO₂RR in the Ni-based SAC.

In this study, we demonstrated that a simple pyrolysis process can modulate the local structure of the Ni-N_x site and types of N configurations in Ni SACs, which affects the catalytic performances of the CO₂RR. To manipulate the atomic environments of Ni SACs, we fabricated three types of samples with Ni ZIF-8 (not heat-treated), Ni SAC-800, and Ni SAC-1000 (after pyrolysis at 800 and 1000 °C). As the pyrolysis temperature increased from 800 to 1000 °C, the coordination number of Ni-N decreased from 3.14 to 2.63 as well as the relative ratio of pyrrolic N/pyridinic N increased from 0.37 to 1.01, indicating that the pyrrolic N can be thermally activated and stabilized in low-coordinated Ni SACs. Ni SAC-1000 showed relatively higher catalytic performances ($FE_{CO} = 98.24\%$ at $-0.8 V_{RHE}$ and $j_{CO} = 148.25 \text{ mA cm}^{-2}$ at $-1.4 V_{RHE}$) compared to that of Ni SAC-800 ($FE_{CO} = 40.76\%$ at $-0.8 V_{RHE}$ and $j_{CO} = 4.41 \text{ mA cm}^{-2}$ at $-1.4 V_{RHE}$) in a microfluidic flow cell system due to the pyrrolic N-stabilized Ni SAC with low coordinated Ni-N_x sites. Because of the continuous contact between CO₂ and the catalyst as well as the fast diffusion of CO₂ gas in the flow cell system, Ni SAC-1000 maintained $FE_{CO} > 95\%$ at potentials from -0.8 to $-1.4 V_{RHE}$

and showed significantly higher current density ($\sim 200 \text{ mA cm}^{-2}$) compared to that of the H-type cell system ($\sim 20 \text{ mA cm}^{-2}$). DFT calculations showed that the synergistic effect between the high content ratio of pyrrolic N and low-coordinated Ni can decrease the energy barrier for the desorption of *CO during the CO₂RR, leading to high production of CO. As a result, the high performance of Ni SAC-1000 in the microfluidic flow cell system presents great chances for scaling up the productivity of CO₂ reduction products toward the industrial level.

Results and discussion

Morphology and microstructure

The Ni SAC was fabricated by solution-based synthesis and a subsequent pyrolysis process, which are schematically outlined in Fig. 1a (synthesis procedures are detailed in the Experimental section). ZIF-8 was fabricated through solution-based synthesis with Ni and Zn precursors, and 2-MeIm. ZIF-8 with a porous structure serves as a molecular cage by trapping the Ni and Zn ions with the organic ligands of 2-MeIm. After the pyrolysis process, a metal (M)-N_x-C structure supported on an N-rich carbon matrix was clearly obtained because the ordered assembly of Ni and Zn was placed in the ZIF-8 structure. To investigate the effect of pyrolysis temperature, we conducted heat treatment at 800 and 1000 °C at a rate of 25 °C min^{-1} and maintained the temperature for 4 h under an Ar atmosphere in a tube furnace (denoted as Ni SAC-800 and Ni SAC-1000). The morphology of Ni ZIF-8 (before pyrolysis), Ni SAC-800, and Ni SAC-1000 was investigated using a FE-SEM. The SEM images showed that the as-prepared samples exhibited similar cubic-like morphology even after the pyrolysis process (Fig. 1b).

The microstructure of the as-prepared samples was further investigated with HR-TEM. It showed a uniform rhombic dodecahedron structure with an average size of approximately 40–50 nm in all samples (Fig. 2a and S1†). However, the morphology started to aggregate because the MOF structure in ZIF-8 changed to an M-N_x-C structure under the pyrolysis process. The insetted SAED patterns revealed an amorphous-like carbon structure, which means that there are not any metal-containing nanoparticles in the carbon matrix. HAADF-STEM analysis was conducted to investigate the atomic distribution of Ni atoms in the as-prepared samples (Fig. 2b). In the Ni ZIF-8 skeleton structure, no bright dots representing isolated single Ni atoms are observed. In contrast, isolated single Ni atoms were clearly distributed in the entire N-rich carbon matrix in both Ni SAC-800 and -1000. Thus, it is important to thermally activate the Ni ZIF-8 structure to achieve highly dispersed Ni single atoms in the M-N_x-C structure. TEM-EDS images showed that the elements of C, N, Zn, and Ni were distributed in the as-prepared samples (Fig. S2†). The elemental content of Ni increased with increasing pyrolysis temperature, which was determined by ICP-AES. It showed that the Ni content was 0.63 wt%, 1.41 wt%, and 2.01 wt% for Ni ZIF-8, Ni SAC-800, and Ni SAC-1000, respectively (Fig. S3 and Table S1†). Notably, most of the Zn species were evaporated during the pyrolysis process, but residual Zn species still remained and could be anchored in



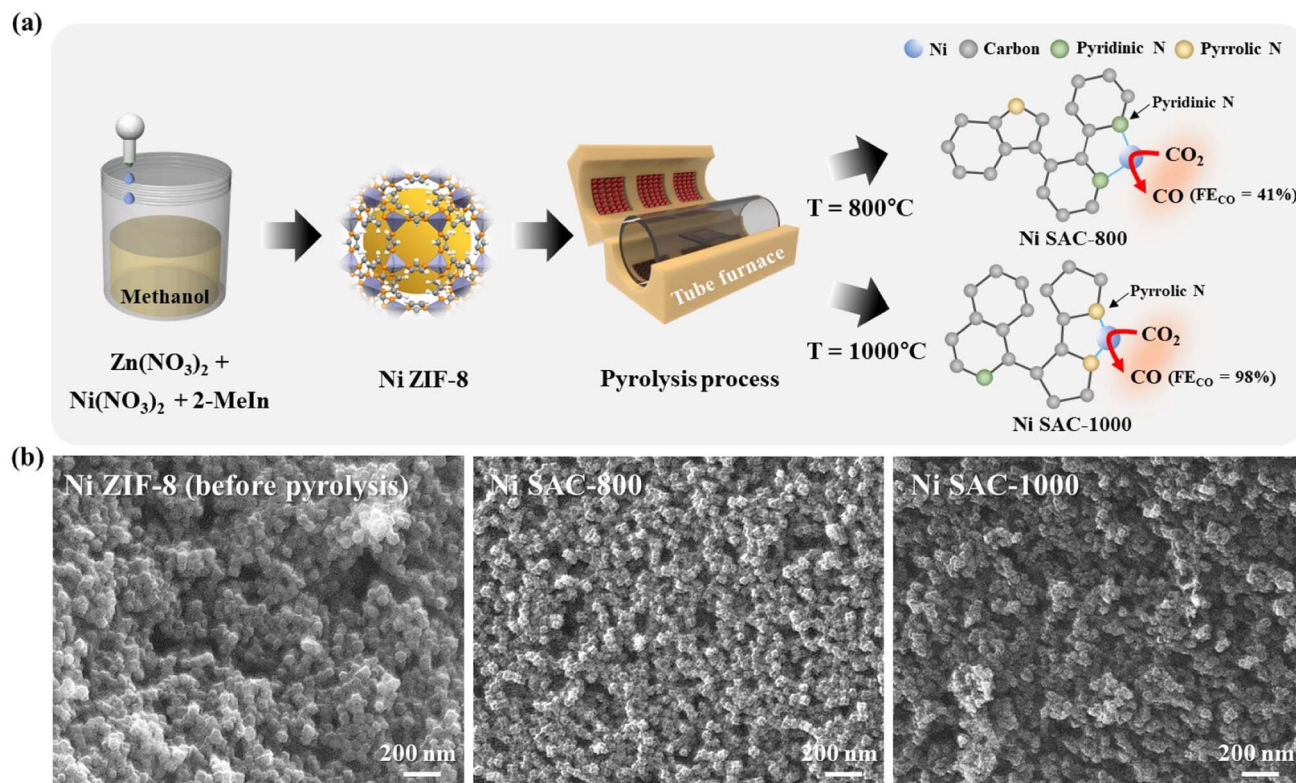


Fig. 1 (a) Schematic illustration of the fabrication process of the pyrrolic N-stabilized low-coordinated Ni SAC and proposed Ni-N_x active site structure. (b) SEM images of Ni ZIF-8 (before pyrolysis) and the Ni SAC (after pyrolysis at 800 and 1000 °C).

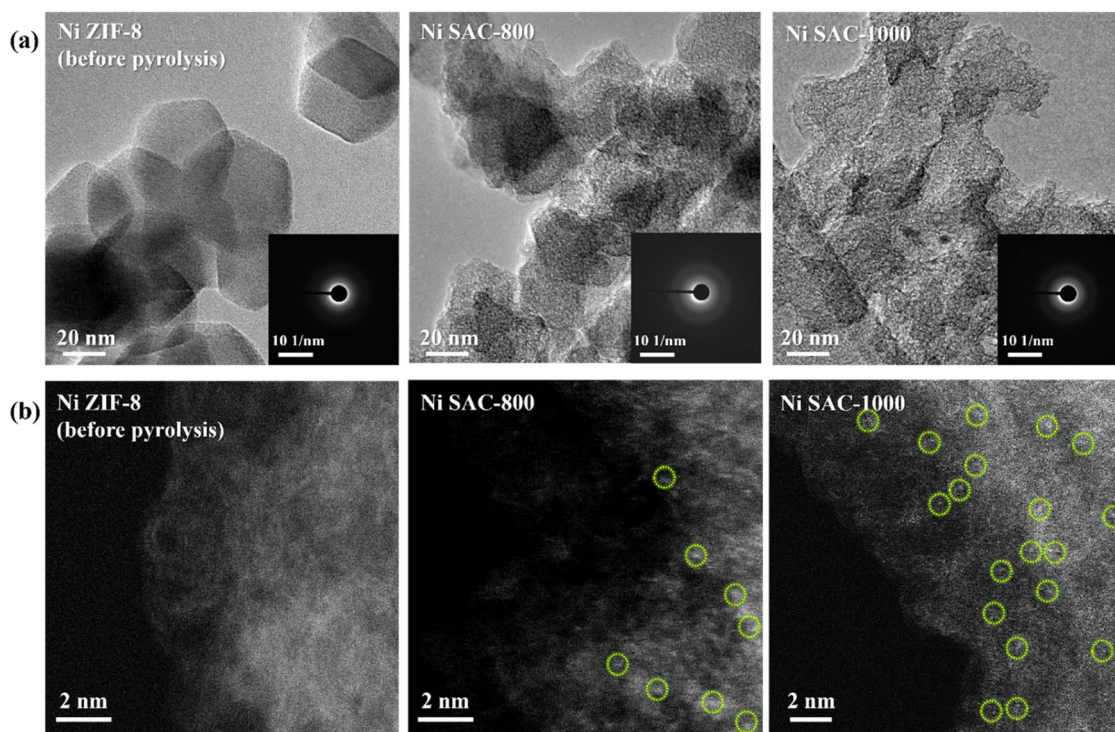


Fig. 2 (a and b) TEM and HAADF-STEM images of Ni ZIF-8 (before pyrolysis) and the Ni SAC (after pyrolysis at 800 and 1000 °C) with the SAED patterns in the inset.



the carbon matrix. The residual Zn can prevent the aggregation of Ni species and plays a role in the construction of the porous structure.²⁸

Crystal structure, chemical compositions, and electronic configuration

The crystal structure was detected by XRD and Raman spectroscopy (Fig. S4[†]). Both Ni SAC-800 and -1000 samples exhibited no diffraction patterns from crystalline Ni and Zn-based nanoparticles. It showed a broad graphitic carbon peak of the (002) plane at 21.5°, which was totally different from the sharp peaks of the ZIF-8 structure. So, there are no peaks of the Ni and Zn metallic phases in Ni SAC-800 and -1000, which were consistent with the results of HR-TEM and HAADF-STEM. The Raman spectra showed a higher integrated area ratio of I_D/I_G for Ni SAC-1000 (1.49) compared to those of Ni SAC-800 (1.13), leading to a higher disordered structure related to the structural defects. As a result, we confirmed that the Ni single atoms are highly distributed on the defect-rich carbon matrix, and they are detected by only HAADF-STEM analysis.

XPS was conducted to elucidate the surface compositions and related valence states of the as-prepared samples (Fig. 3). The Zn 2p spectra of the as-prepared samples contained two peaks centered at 1044.30 and 1021.40 eV, which can be assigned to Zn²⁺ in both Zn 2p_{1/2} and Zn 2p_{3/2} (Fig. S5a[†]).^{22,37} As the pyrolysis temperature increased, the intensity of the Zn 2p spectra gradually decreased but it still remained as also confirmed by TEM-EDS, and the residual Zn plays role in the

prevention of aggregation of Ni species.²⁸ The Ni 2p_{3/2} spectra of the as-prepared samples were deconvoluted into the peaks of Ni²⁺ (856.22 eV), Ni⁺ (855.54 eV), and metallic Ni⁰ (854.28 eV) states (Fig. 3a).^{29,37,38} Ni ZIF-8 (before pyrolysis) showed only the Ni²⁺ peak, which was consistent with the valence state of the MOF structure in reference NiPc. On the other hand, there are three distinct peaks of Ni²⁺, Ni⁺, and metallic Ni⁰ for both Ni SAC-800 and -1000 samples, indicating that the valence state of Ni atoms is likely to be between 0 and +2. Notably, as the pyrolysis temperature increased, the integrated area ratio of Ni⁺/Ni²⁺ increased in the as-prepared samples (Fig. 3c). So, it means that the valence state of Ni atoms in Ni SAC-1000 was relatively lower than that of Ni SAC-800. The N 1s spectra were deconvoluted into seven N-related configurations, originating from graphitic N (403.69 eV), N=C (imidazole) (402.12 eV), pyrrolic N (401.48 eV), N-Ni (400.59 eV), N-Zn (399.13 eV), pyridinic N (398.55 eV), and N-H (imidazole) (398.24 eV), respectively (Fig. 3b).^{25,28,37,39} Ni ZIF-8 showed distinct MOF structure-related peaks of N=C (imidazole) and N-H (imidazole), and they vanished after the pyrolysis because the MOF structure could be changed to a M-N_x-C structure. It is worth noting that the relative ratio of pyrrolic N/pyridinic N was higher in Ni SAC-1000 compared to that of Ni SAC-800, indicating that some of the pyridinic N species were damaged during the pyrolysis process; meanwhile most of the pyrrolic N species remained in Ni SAC samples (Fig. 3d, S5b and Table S1[†]). When the pyridinic N species were removed from the carbon matrix, it will leave several defects such as vacancies and also can be confirmed by Raman spectroscopy results of the I_D/I_G value (Table S2[†]). Thus,

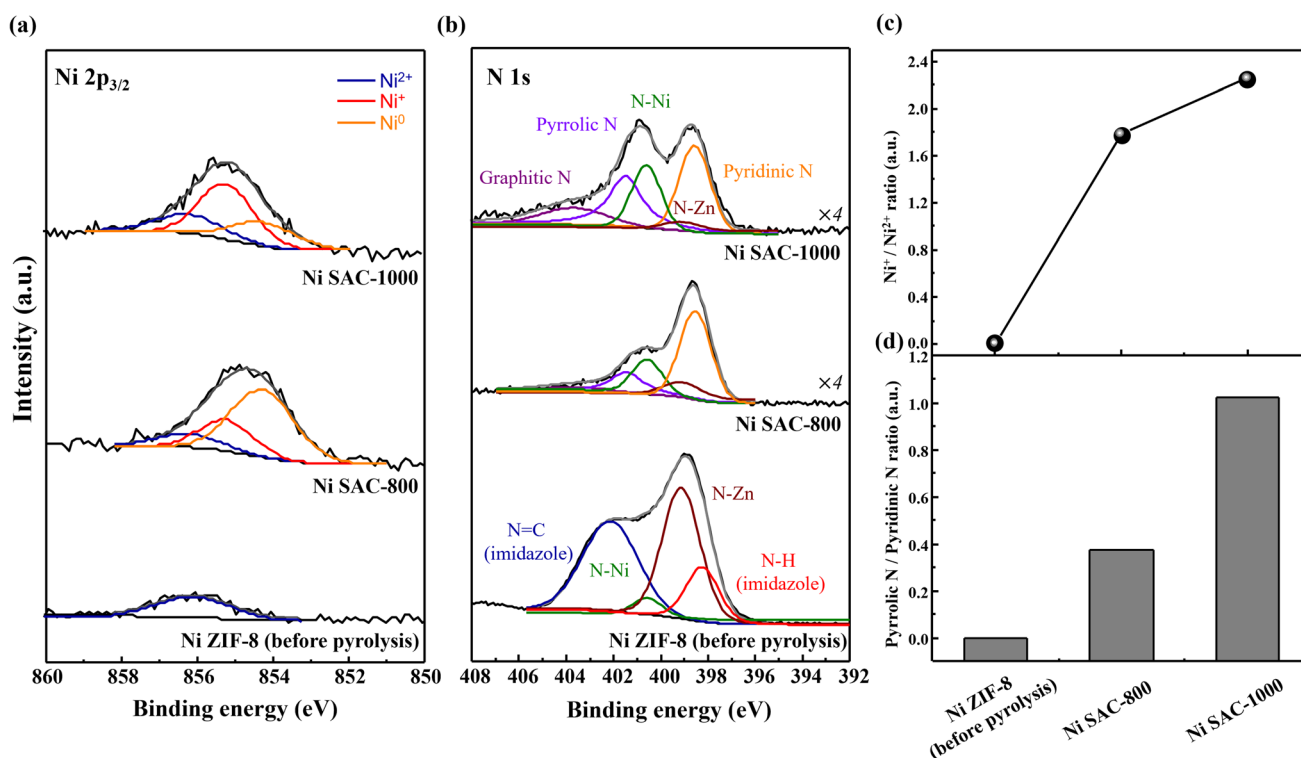


Fig. 3 XPS spectra of (a) Ni 2p_{3/2} and (b) N 1s for Ni ZIF-8 (before pyrolysis) and the Ni SAC (after pyrolysis at 800 and 1000 °C). Relative integrated peak area ratio of (c) Ni⁺/Ni²⁺ content and (d) pyrrolic N/pyridinic N content in Ni-based samples.



it can be concluded that the N configuration coordinated in Ni species is strongly affected by thermal activation energies.

To identify the local electronic structure of the as-prepared samples, we further conducted XANES and EXAFS (Fig. 4). In the Ni K-edge XANES spectra, the near-edge absorption energy of Ni ZIF-8, Ni SAC-800, and Ni SAC-1000 is placed between those of reference Ni foil (Ni^0) and NiPc (Ni^{2+}), indicating a valence state between 0 and +2 (Fig. 4a). Also, the valence state of the as-prepared samples negatively shifted as the pyrolysis temperature increased, suggesting that Ni atoms in Ni SAC-1000 are in a relatively low-valent state compared to the other samples. The coordination environment of Ni atoms in the as-prepared samples was investigated by the corresponding FT-EXAFS. It showed the presence of Ni-N peaks and the absence of Ni-Ni peaks in the Ni SAC samples, indicating that Ni species are distributed at an atomic level in the carbon matrix (Fig. 4b and S6†). The average Ni-N coordination number in Ni ZIF-8, Ni SAC-800, and Ni SAC-1000 is 4.0, 3.14, and 2.63, respectively, suggesting that the Ni atoms were unsaturated with N species after the pyrolysis process (Table S3†). So, it indicated that Ni SAC samples have the configurations of Ni-N_x ($x = 2 \sim 4$) and showed more unsaturated coordination environments in Ni SAC-1000 compared to that of Ni SAC-800. Moreover, after the pyrolysis, Ni-N interatomic distances gradually decreased compared to that of the MOF structure in NiPc (Ni-N_4), suggesting that the pyrolysis process leads to the destruction of the Ni-N₄ structures and forms structural defects in the carbon matrix. Furthermore, through the electron paramagnetic resonance (EPR) measurement technique, the *g*-value is calculated to be 2.14, indicating abundant nitrogen vacancies in Ni SAC-1000 (Fig. S7†). From these results, we conclude that the highly distributed Ni atoms in Ni SAC-1000 have a relatively low-coordinated and low-valent Ni state ($\text{Ni}^{1+}\text{-N}_x$) with a high content of pyrrolic N species compared to that of Ni SAC-800.

Electrochemical CO₂ reduction in a flow cell system

A conventional H-type cell system has a critical issue with restricted current densities by the limited solubility of CO₂ in an aqueous electrolyte. Thus, we employed a GDE-based flow cell system and evaluated the Ni ZIF-8 (before pyrolysis), Ni SAC-800, and Ni SAC-1000 samples to identify the effect of pyrolysis temperature on the catalytic properties of the CO₂RR in a CO₂-purged electrolyte (Fig. 5a). LSV was conducted to investigate the current-related performance of the as-prepared samples in CO₂ and N₂-purged 0.5 M KHCO₃ electrolyte at a scan rate of 100 mV s⁻¹ (Fig. 5b). It showed more negative current densities under the CO₂-purged electrolyte than that under the N₂-purged one. This is because the reduction of CO₂ and H₂O can occur simultaneously under the former conditions but only H₂O could be reduced under the latter one, indicating that there is an activity for CO₂ reduction in all samples. Especially, Ni SAC-1000 showed the highest magnitude of current density among the samples ($\sim 200 \text{ mA cm}^{-2}$) and revealed a relatively higher value compared to that of the H-type cell system. The kinetics of the electron-transfer process were investigated by EIS measurements (Fig. 5c). The first semi-circle in the high-frequency region indicates a capacitive/resistive behavior between the solution, reference electrode, and working electrode constituted by the samples. The second semi-circle in the low-frequency region is the resistance from the charge transfer during an electrocatalytic reaction.^{40,41} The result that the radius of the second semi-circle is the smallest for Ni SAC-1000 means that the charge-transfer activity could be enhanced by increasing the pyrolysis temperature in as-prepared samples. ECSA measurement was conducted to identify the catalytically active surface area for the CO₂RR (Fig. 5d and S8†). The double-layer capacitance (C_{dl}) of Ni SAC-1000 was $13.08 \mu\text{F cm}^{-2}$, which was the highest value among the samples.



Fig. 4 (a) Ni K-edge XANES spectra of Ni ZIF-8 (before pyrolysis), the Ni SAC (after pyrolysis at 800 and 1000 °C), and reference Ni foil and NiPc samples. (b) FT-EXAFS spectra of the Ni K-edge for Ni-based samples in the *R* space.





Fig. 5 (a) High-rate CO₂ electrolysis with a gas and electrolyte-feed flow cell system for Ni-based samples. The results of (b) LSV, (c) Nyquist impedance, and (d) ECSA measurements for Ni ZIF-8 (before pyrolysis) and the Ni SAC (after pyrolysis at 800 and 1000 °C).

So, the larger active surface area of Ni SAC-1000 is one of the reasons for enhanced catalytic activity. The faradaic efficiencies (FEs) of the as-prepared samples were characterized at different applied potentials from -0.4 to -1.4 V_{RHE} in CO₂-purged 0.5 M KHCO₃ electrolyte (Fig. 6a). Before pyrolysis, Ni ZIF-8 primarily produces H₂ (FE_{H₂} > 40%) with only a trace amount of CO (FE_{CO} < 10%). After pyrolysis at 800 °C, the FE_{CO} of Ni SAC-800 improved as high as 40.76% at -0.8 V_{RHE}. As the pyrolysis temperature further increased to 1000 °C, the FE_{CO} of Ni SAC-1000 drastically increased to a maximum value of 98.24% at -0.8 V_{RHE}, due to the increased content of catalytically active pyrrolic N species and abundant structural defects in Ni SAC-1000. Also, Ni SAC-1000 showed the highest partial current density of CO among the samples ($j_{\text{CO}} = 148.25$ mA cm⁻² at -1.4 V_{RHE}) (Fig. 6b). The high selectivity and current density are due to the significantly suppressed H₂ evolution in Ni SAC-1000 (FE_{H₂} < 5% at all applied potentials) (Fig. 6c and Table S4†). For practical applications, the stability of catalysts is important for the CO₂RR in CO₂-purged electrolytes. The stability of Ni SAC-1000 was evaluated for 24 h at a constant potential of -0.8 V_{RHE} in CO₂-purged 0.5 M KHCO₃ (Fig. 6d). To maintain the pH

value of the electrolyte, CO₂ gas was continuously provided to the electrolyte during the reaction. The total current density was almost constant for 24 h (~ 50 mA cm⁻² at -0.8 V_{RHE}) and a high FE_{CO} of $\sim 95\%$ was consistently obtained in long-term reactions. Moreover, there was negligible change in the morphology, crystal structure, and atomic environment of Ni SAC-1000 before and after the reaction for 24 h, indicating that Ni SAC-1000 maintained its catalytic activities and chemical stability for a long-term reaction in the microfluidic flow cell system (Fig. S9†). Thus, the thermal activation in the as-prepared samples was found to be beneficial not only for the catalytic activity but also for excellent stability. Furthermore, we investigated the electrochemical stability of Ni-SAC-1000 through 1000 cycles in cyclic voltammetry (CV), confirming its ability to impede nickel aggregation (Fig. S10†).

Up to now, the study of transition metal-based SACs has been mainly conducted by using a conventional H-type cell system (Fig. 6e and Table 1). However, scaling up of the productivity of CO₂ reduction products such as CO is limited in a traditional H-type cell because it requires larger overpotentials and the CO₂ mass diffusion can be restricted in the electrolytes.



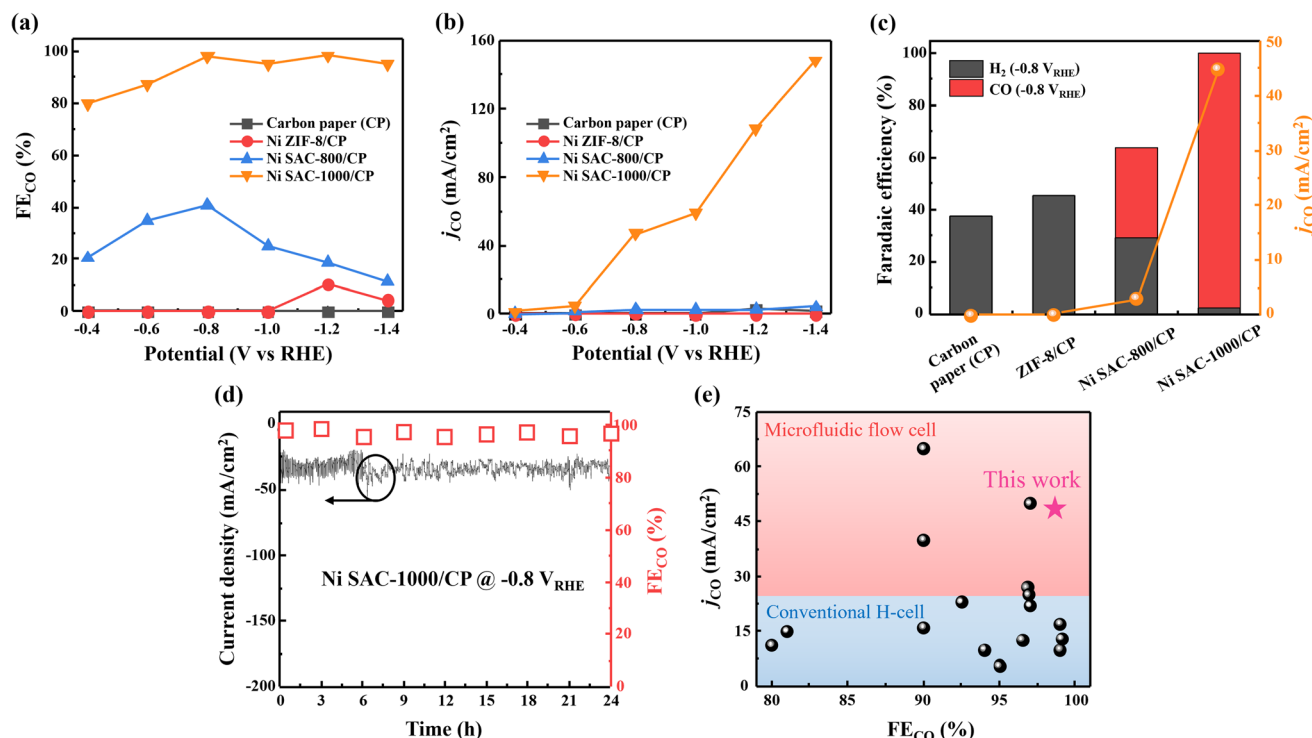


Fig. 6 (a) FE_{CO} and (b) j_{CO} at various applied potentials for Ni-based samples in CO_2 -purged 0.5 M $KHCO_3$ electrolytes. (c) Catalytic activities of Ni-based samples before and after pyrolysis at $-0.8 V_{RHE}$. (d) Stability of Ni SAC-1000 at $-0.8 V_{RHE}$ in CO_2 -purged 0.5 M $KHCO_3$. Current density (solid line) and FE_{CO} (symbol) at $-0.8 V_{RHE}$ were plotted as a function of reaction time. (e) Summary of the catalytic activities of the Ni-based SAC for the production of CO measured with a conventional H-cell and microfluidic flow cell system.

Table 1 Summary of the performances of recent Ni-based SACs for the CO_2RR toward CO

Catalyst	FE_{CO} (%)	j_{CO} ($mA\ cm^{-2}$)	Potential (V)	Electrolyte	Cell system	Ref.
Ni–N–C	94%	$\sim 10\ mA\ cm^{-2}$	$-0.60\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Adv. Funct. Mater.</i> , 2022, 32 , 2202351
Ni–Zn–N–V	99%	$17\ mA\ cm^{-2}$	$-0.80\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Adv. Mater.</i> , 2021, 33 , 2102212
Ni-SAC@NC	95%	$5.7\ mA\ cm^{-2}$	$-0.60\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Appl. Catal. B: Environ.</i> , 2022, 304 , 120997
Ni–N–CNSs	95%	$5.5\ mA\ cm^{-2}$	$-0.75\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>J. Colloid Interface Sci.</i> , 2020, 570 , 31–40
Ni(NC)-1	99%	$\sim 10\ mA\ cm^{-2}$	$-0.75\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>ACS Catal.</i> , 2020, 10 , 1086–1093
Ni@NCNTs	99.1%	$\sim 13\ mA\ cm^{-2}$	$-0.90\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Carbon</i> , 2019, 150 , 52–59
Ni/NC	96.5%	$12.6\ mA\ cm^{-2}$	$-0.90\ V_{RHE}$	0.1 M $KHCO_3$	H-cell	<i>ACS Sustainable Chem. Eng.</i> , 2019, 7 , 15030–15035
Ni-NC_ATPA@C	90%	$\sim 16\ mA\ cm^{-2}$	$-0.90\ V_{RHE}$	0.5 M $NaHCO_3$	H-cell	<i>Chem. Sci.</i> , 2018, 9 , 8775–8780
Ni–N–C	80%	$11.2\ mA\ cm^{-2}$	$-0.75\ V_{RHE}$	0.1 M $KHCO_3$	H-cell	<i>Nat. Commun.</i> , 2017, 8 , 944
Ni–N–C	97%	$22\ mA\ cm^{-2}$	$-0.72\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Nat. Energy</i> , 2018, 3 , 140–147
Ni–N–C	81%	$15\ mA\ cm^{-2}$	$-0.84\ V_{RHE}$	0.1 M $KHCO_3$	H-cell	<i>Energy Environ. Sci.</i> , 2019, 12 , 640–647
Ni1–N–C	96.8%	$27\ mA\ cm^{-2}$	$-0.80\ V_{RHE}$	0.5 M $KHCO_3$	H-cell	<i>Angew. Chem. Int. Ed.</i> , 2020, 59 , 20589–20595
NiN–graphene layers	90%	$65\ mA\ cm^{-2}$	$-0.79\ V_{RHE}$	0.5 M $KHCO_3$	Flow cell	<i>Chem</i> , 2017, 3 , 950
Ni ₃ N/C	92.5%	$23\ mA\ cm^{-2}$	$-0.79\ V_{RHE}$	0.5 M $NaCl$	Flow cell	<i>ACS Appl. Mater. Interfaces</i> , 2018, 10 , 38024–38031
Ni–NG	97%	$50\ mA\ cm^{-2}$	$2.80\ V_{cell}$	0.5 M $KHCO_3$	Flow cell	<i>Energy Environ. Sci.</i> , 2018, 11 , 893–903
ZnNi–DCN-1000	90%	$\sim 40\ mA\ cm^{-2}$	$-0.50\ V_{RHE}$	1 M KOH	Flow cell	<i>Adv. Funct. Mater.</i> , 2022, 32 , 2203842
Ni-SA/NC	96.9%	$\sim 25\ mA\ cm^{-2}$	$-0.66\ V_{RHE}$	1 M KOH	Flow cell	<i>Nano Energy</i> , 2021, 82 , 105689
Pyrrolic N-stabilized Ni SAC	98.2%	$45.03\ mA\ cm^{-2}$	$-0.80\ V_{RHE}$	0.5 M $KHCO_3$	Flow cell	This work
	95.1%	$148.25\ mA\ cm^{-2}$	$-1.40\ V_{RHE}$			

In this work, we employed a 3-compartment microfluidic flow cell reactor, which contained a circulated anolyte, catholyte, and continuous gas-phase CO_2 supply, to boost the current density while maintaining high CO selectivity. Ni SAC-1000 maintained

$FE_{CO} > 95\%$ at potentials from -0.8 to $-1.4 V_{RHE}$ and showed significantly higher current density ($\sim 200\ mA\ cm^{-2}$) compared to that of the H-type cell system ($\sim 20\ mA\ cm^{-2}$) (Fig. S11†). Thus, the high performance of Ni SAC-1000 in the microfluidic



flow cell system provides great opportunities for scaling up the productivity of CO₂ reduction products toward the industrial level.

DFT calculations




To identify the reason for the increased catalytic activity of Ni SAC-1000 compared to that of Ni SAC-800 in the CO₂RR, we have



Fig. 7 (a) Free-energy profiles for the CO₂RR to CO on Ni SACs with different Ni-N_x coordination environments. (b) Optimized calculation models for pyrrolic N stabilized Ni SACs with Ni-N₂V₂ sites. (c) Charge density difference plot on CO adsorbed Ni-N₂V₂ with pyrrolic N configuration, where yellow-colored and cyan-colored isosurfaces represent the boundary of the charge depletion region and charge accumulation region, respectively. (d) Sliced 2-dimensional charge density difference plot of a CO adsorbed single atom Ni site.



to consider the effect of the coordination environment of Ni species (Ni-N) and the ratio of pyrrolic N/pyridinic N in the carbon matrix. Thus, DFT calculations were employed to understand the enhanced selectivity of CO on Ni SAC-1000 (Fig. 7). For the study, we considered possible reaction mechanisms for the CO₂RR in the 2e⁻ reduction pathway to produce CO.⁴² First, adsorbed gaseous CO₂ on the catalytic surface is reduced to the *COOH intermediate by a proton-coupled electron transfer reaction. The *COOH can be further reduced to the *CO intermediate by an additional proton/electron from the electrolyte and lastly, the *CO intermediate detached from the catalytic surface, resulting in the formation of gaseous CO products.⁴³ Previous studies suggested that the rate-determining step (RDS) could be the reaction (1), (2), or (4) depending on the binding energy of the reaction intermediate.⁴⁴



Especially, the step for desorption of the *CO intermediate is critical because the binding energy of *CO on the catalytic surface can tune the selectivity of the CO₂RR products. The relatively weak binding of *CO (low desorption energy of *CO) can produce gaseous CO; meanwhile strongly bonded *CO (high desorption energy of *CO) could suppress CO production. Therefore, it is important to reduce the energy barrier of the *CO desorption step to achieve high selectivity of CO production.⁴⁵

In our DFT calculations, we compared the Gibbs free energy change (ΔG) of reaction intermediates of *COOH and *CO on the Ni SAC on various Ni-N configurations (Fig. 7a).

In terms of the *CO desorption step, it showed that the reaction barrier of desorption of the *CO intermediate is relatively smaller in pyrrolic N sites compared to those of pyridinic N sites regardless of containing vacancies. Notably, Ni-N₂V₂ with pyrrolic N sites revealed the favorable formation of CO products due to its lowest desorption energy of the *CO intermediate (Fig. 7b). In our study, when the pyrolysis temperature increased from 800 °C (Ni SAC-800) to 1000 °C (Ni SAC-1000), the content ratio of pyrrolic N/pyridinic N increased from 0.37 to 1.01 as well as the coordination number of Ni in Ni-N_x sites decreased from 3.14 to 2.63. We additionally conducted charge density generation calculation on *CO adsorbed Ni-N₂V₂-pyrrolic (adsorbate + slab), CO (adsorbate), and Ni-N₂V₂-pyrrolic (slab). Then we calculated the charge density difference induced by the CO adsorption by volumetric subtraction of the spatial charge density of Ni-N₂V₂-pyrrolic (slab) and CO (adsorbate) from that of *CO adsorbed Ni-N₂V₂-pyrrolic (adsorbate + slab), which was then plotted as a charge density difference plot in Fig. 7. The yellow-colored isosurface of Fig. 7c represents the boundary of the charge depletion region,

which matches with the positive oxidation state of the Ni single atom center. The cyan-colored isosurface represents the boundary of the charge accumulation region and the strong bond bridged with accumulated electron density between Ni and C of the CO adsorbate was confirmed in the 2-dimensional sliced charge density plot in Fig. 7d. As a result, we conclude that the synergistic effect between the high content ratio of pyrrolic N and low-coordinated Ni can decrease the energy barrier for the desorption of the *CO intermediate during the CO₂RR, leading to high production of CO in Ni SAC-1000 (FE_{CO} = 98.24% at -0.8 V_{RHE} and j_{CO} = 148.25 mA cm⁻² at -1.4 V_{RHE}) compared to that of Ni SAC-800 (FE_{CO} = 40.76% at -0.8 V_{RHE} and j_{CO} = 4.41 mA cm⁻² at -1.4 V_{RHE}).

Spin-polarized partial density of states (PDOS) calculations on 5 configurations without adsorbed intermediates, namely pristine (a) Ni-N₂V₂-pyrrolic, (b) Ni-N₃V₁-pyrrolic, (c) Ni-N₄-pyrrolic, (d) Ni-N₃V₁-pyridinic, and (e) Ni-N₄-pyridinic, are plotted in Fig. S12.† We calculated the Ni d-band center position and it turned out that if the Ni d-band center position was closer to the Fermi-level, the reaction energy barrier of the CO₂ to CO pathway was reduced. The Ni d-band center of Ni-N₂V₂-pyrrolic configuration was calculated to be -0.71 eV, which was the lowest among the 5 pristine configurations without adsorbed intermediates and showed the lowest reaction energy barrier of 0.149 eV toward the CO pathway. In contrast, Ni-N₄-pyridinic configuration showed the largest reaction energy barrier of 1.112 eV toward the CO pathway and the lowest Ni d-band center position of -2.09 eV. The closer Ni d-band center to the Fermi level induces the optimal *CO binding strength *via* orbital coupling with the C and O orbitals of the adsorbate near the Fermi level, which eventually leads to the facile adsorption and desorption of *CO at the same time. We also conducted partial density of states calculations on 5 different configurations with adsorbed CO on the Ni site and calculated the Ni d-band center in Fig. S13.†

The HCOOH production pathway and H₂ evolution reaction pathway are the two representative competing reactions toward the electroreduction of CO₂ to CO pathway, and we revisited our structural models and placed adsorbates for those competing reactions (Fig. S14†). It turned out that the reaction energy barrier for both HCOOH production and H₂ evolution reaction pathways is higher than that of the CO₂ to CO pathway, which ensured outstanding selectivity and faradaic efficiencies toward CO higher than 95%.

Conclusions

In summary, we have demonstrated a pyrrolic N-stabilized Ni SAC with low-coordinated Ni-N_x sites by using a thermal activation of Ni ZIF-8. We found that Ni SAC-800 and -1000 showed atomically dispersed Ni species with low-coordinated N sites in the carbon matrix and inhibited the formation of Ni nanoparticles as confirmed by HAADF-STEM and XAS. As the pyrolysis temperature increased from 800 to 1000 °C, the coordination number of Ni-N_x sites decreased from 3.14 to 2.63 and increased to a relative content ratio of pyrrolic N/pyridinic N from 0.37 to 1.01. The synergistic effect between the



low-coordinated Ni-N_x sites and the high content ratio of pyrrolic N/pyridinic N decreases the energy barrier for the desorption of the *CO intermediate during the CO₂RR, which enhanced the catalytic performances in Ni SAC-1000 (FE_{CO} = 98.24% at -0.8 V_{RHE}) compared to that of Ni SAC-800 (FE_{CO} = 40.76% at -0.8 V_{RHE}). Moreover, we employed a microfluidic flow cell system to boost catalytic productivity at the industrial level. Ni SAC-1000 showed relatively outstanding current density (~200 mA cm⁻²) in the flow cell system compared to that of conventional H-type cell configuration (~20 mA cm⁻²). The FE_{CO} keeps well above 95% at potentials from -0.8 to -1.4 V_{RHE} and it showed excellent stability to produce CO during long-term operation for 24 h. This work experimentally demonstrated the relationship between local N configuration in Ni-N_x sites and catalytic activities for the CO₂RR in a flow cell system, providing guidelines for designing highly productive CO selective Ni SACs.

Author contributions

J. W. Lim, D. H. Choo, and J. H. Cho conceptualized the idea and experimental design. J. W. Lim and J. H. Cho, with support from S. Lee, K. Kim, J. Son, and S. Y. Choi, prepared the catalysts and assessed the electrochemical CO₂ reduction performances. W. S. Cho and O. F. N. Okello contributed to the material characterization of the catalysts. J. Kim conducted the DFT calculations under the supervision of H. W. Jang and S. Y. Kim. The overall work was supervised by J. K. Kim and J.-L. Lee, with all authors actively participating in the discussion of the results.

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

This work was supported by the Korea Institute of Energy Technology Evaluation and Planning (KETEP) and the Ministry of Trade, Industry & Energy (MOTIE) of the Republic of Korea (20212010100040), and in part by the Brain Korea 21 PLUS project for Education and Research center for future materials (F21YY7105002), and in part by the National Research Foundation of Korea (NRF) grant funded by the Korea government (MSIT) (RS-2023-00209139).

References

- 1 A. Al-Mamoori, A. Krishnamurthy, A. A. Rownaghi and F. Rezaei, *Energy Technol.*, 2017, **5**, 834–849.
- 2 W. S. Cho, D. M. Hong, W. J. Dong, T. H. Lee, C. J. Yoo, D. Lee and J.-L. Lee, *Energy Environ. Mater.*, 2024, **7**, e12490.
- 3 F. M. Baena-Moreno, M. Rodríguez-Galán, F. Vega, B. Alonso-Fariñas, L. F. V. Arenas and B. Navarrete, *Energy Sources, Part A*, 2019, **41**, 1403–1433.
- 4 J. W. Lim, W. J. Dong, J. Y. Park, D. M. Hong and J.-L. Lee, *ACS Appl. Mater. Interfaces*, 2020, **12**, 22891–22900.
- 5 J. W. Lim, W. J. Dong, W. S. Cho, C. J. Yoo and J.-L. Lee, *ACS Catal.*, 2022, **12**, 13174–13185.
- 6 M. E. Dry, *J. Chem. Technol. Biotechnol.*, 2002, **77**, 43–50.
- 7 J. Y. Park, W. J. Dong and J.-L. Lee, *ACS Appl. Energy Mater.*, 2022, **5**, 1627–1634.
- 8 J. Y. Park, W. J. Dong, S.-M. Jung, Y.-T. Kim and J.-L. Lee, *Appl. Catal., B*, 2021, **298**, 120586.
- 9 W. J. Dong, J. W. Lim, J. Y. Park, C. J. Yoo, S. Baek, W. S. Cho, W. Kim and J.-L. Lee, *Appl. Surf. Sci.*, 2021, **565**, 150460.
- 10 C. J. Yoo, W. J. Dong, J. Y. Park, J. W. Lim, S. Kim, K. S. Choi, F. O. O. Ngome, S.-Y. Choi and J.-L. Lee, *ACS Appl. Energy Mater.*, 2020, **3**, 4466–4473.
- 11 T. S. Safaei, A. Mepham, X. Zheng, Y. Pang, C.-T. Ding, M. Liu, D. Sinton, S. O. Kelley and E. H. Sargent, *Nano Lett.*, 2016, **16**, 7224–7228.
- 12 Y. Liu, J. Zhao, Z. Li, C. Mu, W. Ma, H. Hu, K. Jiang, H. Lin, H. Ade and H. Yan, *Nat. Commun.*, 2014, **5**, 1–6.
- 13 W. J. Dong, C. J. Yoo, J. W. Lim, J. Y. Park, K. Kim, S. Kim, D. Lee and J.-L. Lee, *Nano Energy*, 2020, **78**, 105168.
- 14 D. H. Won, H. Shin, J. Koh, J. Chung, H. S. Lee, H. Kim and S. I. Woo, *Angew. Chem., Int. Ed.*, 2016, **55**, 9297–9300.
- 15 T. Zheng, K. Jiang and H. Wang, *Adv. Mater.*, 2018, **30**, 1802066.
- 16 W. J. Dong, J. W. Lim, D. M. Hong, J. Kim, J. Y. Park, W. S. Cho, S. Baek and J.-L. Lee, *ACS Appl. Mater. Interfaces*, 2021, **13**, 18905–18913.
- 17 J. Rosen, G. S. Hutchings, S. Rivera, Y. Zhou, D. G. Vlachos and F. Jiao, *ACS Catal.*, 2015, **5**, 4293–4299.
- 18 M. Ma, K. Liu, J. Shen, R. Kas and W. A. Smith, *ACS Energy Lett.*, 2018, **3**, 1301–1306.
- 19 T. Zheng, K. Jiang, N. Ta, Y. Hu, J. Zeng, J. Liu and H. Wang, *Joule*, 2019, **3**, 265–278.
- 20 R. Boppella, M. A. P. Y. Kim, E. Kim, I. Song, Y. Eom, P. Kumar, M. Balamurugan, E. Sim, D. H. Kim and T. K. Kim, *Adv. Funct. Mater.*, 2022, **32**, 2202351.
- 21 B. Wulan, X. Cao, D. Tan, X. Shu and J. Zhang, *Adv. Funct. Mater.*, 2022, **32**, 2203842.
- 22 Q. Wang, T. Ina, W.-T. Chen, L. Shang, F. Sun, S. Wei, D. S. Waterhouse, S. G. Telfer, T. Zhang and G. I. N. Waterhouse, *Sci. Bull.*, 2020, **65**, 1743–1751.
- 23 Y. Guo, S. Yao, Y. Xue, X. Hu, H. Cui and Z. Zhou, *Appl. Catal., B*, 2022, **304**, 120997.
- 24 S. Li, M. Ceccato, X. Lu, S. Frank, N. Lock, A. Roldan, X.-M. Hu, T. Skrydstrup and K. Daasbjerg, *J. Mater. Chem. A*, 2021, **9**, 1583–1592.
- 25 Y. J. Sa, H. Jung, D. Shin, H. Y. Jeong, S. Ringe, H. Kim, Y. J. Hwang and S. H. Joo, *ACS Catal.*, 2020, **10**, 10920–10931.
- 26 S. A. Abbas, J. T. Song, Y. C. Tan, K. M. Nam, J. Oh and K.-D. Jung, *ACS Appl. Energy Mater.*, 2020, **3**, 8739–8745.
- 27 H. Yang, Q. Lin, C. Zhang, X. Yu, Z. Cheng, G. Li, Q. Hu, X. Ren, Q. Zhang, J. Liu and C. He, *Nat. Commun.*, 2020, **11**, 593.
- 28 C. Yan, H. Li, Y. Ye, H. Wu, F. Cai, R. Si, J. Xiao, S. Miao, S. Xie, F. Yang, Y. Li, G. Wang and X. Bao, *Energy Environ. Sci.*, 2018, **11**, 1204–1210.
- 29 H. B. Yang, S.-F. Hung, S. Liu, K. Yuan, S. Miao, L. Zhang, X. Huang, H.-Y. Wang, W. Cai, R. Chen, J. Gao, X. Yang,



- W. Chen, Y. Huang, H. M. Chen, C. M. Li, T. Zhang and B. Liu, *Nat. Energy*, 2018, **3**, 140–147.
- 30 P. P. Sharma, J. Wu, R. M. Yadav, M. Liu, C. J. Wright, C. S. Tiwary, B. I. Yakobson, J. Lou, P. M. Ajayan and X.-D. Zhou, *Angew. Chem., Int. Ed.*, 2015, **127**, 13905–13909.
- 31 C. Zhao, X. Dai, T. Yao, W. Chen, X. Wang, J. Wang, J. Yang, S. Wei, Y. Wu and Y. Li, *J. Am. Chem. Soc.*, 2017, **139**, 8078–8081.
- 32 X. Li, W. Bi, M. Chen, Y. Sun, H. Ju, W. Yan, J. Zhu, X. Wu, W. Chu, C. Wu and Y. Xie, *J. Am. Chem. Soc.*, 2017, **139**, 14889–14892.
- 33 D. Voiry, H. S. Shin, K. P. Loh and M. Chhowalla, *Nat. Rev. Chem*, 2018, **1**, 0105.
- 34 L. Jiao, W. Yang, G. Wan, R. Zhang, X. Zheng, H. Zhou, S.-H. Yu and H.-L. Jiang, *Angew. Chem., Int. Ed.*, 2020, **59**, 20589–20595.
- 35 K. Jiang, S. Siahrostami, T. Zheng, Y. Hu, S. Hwang, E. Stavitski, Y. Peng, J. Dynes, M. Gangisetty, D. Su, K. Attenkofer and H. Wang, *Energy Environ. Sci.*, 2018, **11**, 893–903.
- 36 C.-T. Dinh, T. Burdyny, M. G. Kibria, A. Seifaitokaldani, C. M. Gabardo, F. P. G. D. Arquer, A. Kiani, J. P. Edwards, P. D. Luna, O. S. Bushuyev, C. Zou, R. Q. Bermudez, Y. Pang, D. Sinton and E. H. Sargent, *Science*, 2018, **360**, 783–787.
- 37 B. Shen, B. Wang, L. Zhu and L. Jiang, *Nanomaterials*, 2020, **10**, 1636.
- 38 X. Wu, J. Chen, M. Wang, X. Li, L. Yang, G. Li, L. Shan, X. Li, Y. Lin and J. Jiang, *Chem. Commun.*, 2022, **58**, 2914–2917.
- 39 D. Muñoz-Gil and F. M. L. Figueiredo, *Nanomaterials*, 2019, **9**, 1369.
- 40 B. Hirschorn, M. E. Orazem, B. Tribollet, V. Vivier, I. Frateur and M. Musiani, *Electrochim. Acta*, 2010, **55**, 6218–6227.
- 41 A. Sacco, *J. CO₂ Util.*, 2018, **27**, 22–31.
- 42 Q. Lu and F. Jiao, *Nano Energy*, 2016, **29**, 439–456.
- 43 X. Wang, Z. Mao, G. Wei, Y. Zhang, B. Li, L. Zhu, S.-M. Xu, J. Jiang and S. Tang, *Appl. Surf. Sci.*, 2023, **639**, 158243.
- 44 S. Liang, L. Huang, Y. Gao, Q. Wang and B. Liu, *Adv.Sci.*, 2021, **8**, 2102886.
- 45 Y. Zhang, T. Liu, X. Wang, Q. Dang, M. Zhang, S. Zhang, X. Li, S. Tang and J. Jiang, *ACS Appl. Mater. Interfaces*, 2022, **14**, 9073–9083.

