



Cite this: *Chem. Soc. Rev.*, 2016, 45, 1036

Received 18th August 2015

DOI: 10.1039/c5cs00651a

www.rsc.org/chemsocrev

Solution based CVD of main group materials

Caroline E. Knapp and Claire J. Carmalt*

This critical review focuses on the solution based chemical vapour deposition (CVD) of main group materials with particular emphasis on their current and potential applications. Deposition of thin films of main group materials, such as metal oxides, sulfides and arsenides, have been researched owing to the array of applications which utilise them including solar cells, transparent conducting oxides (TCOs) and window coatings. Solution based CVD processes, such as aerosol-assisted (AA)CVD have been developed due to their scalability and to overcome the requirement of suitably volatile precursors as the technique relies on the solubility rather than volatility of precursors which vastly extends the range of potentially applicable compounds. An introduction into the applications and precursor requirements of main group materials will be presented first followed by a detailed discussion of their deposition reviewed according to this application. The challenges and prospects for further enabling research in terms of emerging main group materials will be discussed.

1 Introduction

Thin films incorporating main group elements play a critical role in many current and potential applications. This is particularly true for electronic applications with semiconductors based on combinations of elements from Groups III and V, III and VI, II and VI and IV and VI having significant impact on our every day lives.

These materials, including gallium nitride (GaN), gallium arsenide (GaAs) and copper indium gallium selenide (CIGS) are utilised in a wide range of applications in solar cells, satellite TV receivers, optical fibre communications and full colour advertising displays. Similarly, transparent conducting oxides (TCOs) play a key role in many optoelectronic devices due to their unique combination of transparency in the visible region of the spectrum and electrical conductivity. These metal oxide thin films, dominated by main group oxides like indium tin oxide (ITO) and fluorine-doped tin oxide (FTO), are ideal for applications in displays and photovoltaics.

Department of Chemistry, University College London, 20 Gordon Street, London WC1H 0AJ, UK. E-mail: c.j.carmalt@ucl.ac.uk



Caroline E. Knapp

and Ivan Parkin. She was awarded a Ramsay Fellowship in 2015 and now carries out research isolating novel precursors for the printing of electronic devices.

Caroline Knapp gained her MSci and then PhD from UCL in the field of precursor design and analysis with Professors Claire Carmalt and Paul McMillan. Following this she worked on low valent group 14 chemistry at UC Davis, CA, with Professor Phil P. Power. She returned to the UK, firstly with a post doc. at Imperial College under the supervision of Dr. Joachim Steinke and secondly back at UCL, under the supervision of Professors Carmalt



Claire J. Carmalt

reviews/contributions to books. Her group's research involves the development of innovative new routes to technologically important inorganic materials focusing on the synthesis of "designed" molecular precursors and Aerosol Assisted Chemical Vapour Deposition.

Claire Carmalt is a Professor of Inorganic Chemistry at University College London (UCL). She is currently the Head of the Inorganic & Materials section and Vice Dean (Education), Mathematical & Physical Sciences Faculty. She obtained her BSc and PhD from the University of Newcastle upon Tyne and was a postdoctoral fellow at the University of Austin at Texas. She has published over 190 research papers and 10



development of precursors requires investigation into purification techniques and potentially alternative synthetic routes to achieve highly pure compounds. For scale up and use in industry, the precursor must be able to be prepared and isolated readily in large quantities, and with minimal environmental or cost implications. Stability and low toxicity of the precursor are also important for ease of use and storage.

CVD processes traditionally involved the use of dual source precursors but efforts to lower the growth temperature resulted in the development of single-source precursors, which already contain an M–E (*e.g.* M = group 12, 13, 14 element; E = N, P, As, Sb, S, Se *etc.*) bond at the core of the molecule, with various other ligands attached to each of the elements. The desired reaction pathway involves adsorption of the precursor without breaking the M–E bond but with loss of the ancillary ligands. Single-source precursors potentially display a range of advantages over conventional CVD precursors, including:

- However, commercialisation of single-source precursors are still limited due to their disadvantages, including:

- Difficulties in control of stoichiometry using single-source precursors, such as in the growth of ternary and quaternary materials, for example $\text{In}_x\text{Ga}_{1-x}\text{As}_x$.
- Low volatility, such that the use of established MOCVD equipment is difficult.
- Low surface mobility of polynuclear decomposition fragments can prevent epitaxial growth.

This review examines the use of AACVD as a method for the deposition of thin films of main group materials. The influence of precursors utilised and deposition conditions employed on film characteristics is discussed and applications to which AACVD has been found beneficial will be highlighted. This review aims to summarise recent achievements of AACVD in the preparation of these main group materials, and to present some ideas regarding future prospects. The review is organised to provide an overview of the deposition of thin films of main group materials, grouped according to their application. The importance of morphological control, from the selection of precursors used to deposition conditions chosen is key for best performance in the targeted technological applications; which are discussed in the order: main group semiconductors, TCOs, PEC materials and gas sensors.

In order to limit potential contamination in deposited thin films a crucial requirement for a precursor is its purity. Hence,

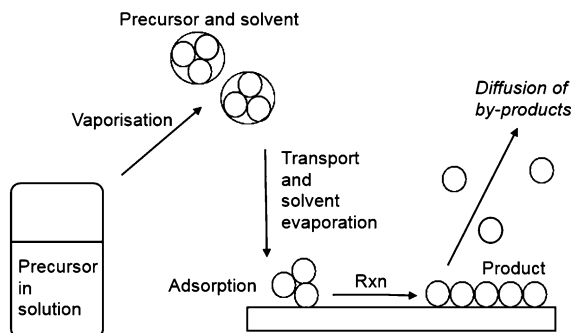


Fig. 1 Schematic illustration of the process involved in AACVD.

eliminated many of the disadvantages traditionally associated with single-source precursors (volatility, control of stoichiometry). The conditions applied during deposition in an AACVD process can greatly affect the microstructure of the film with the morphology of the deposited films depending on a range of factors, including temperature, solvent, substrate and the precursor.

3 Main group semiconductors


Informative reviews of the growth techniques and structural, electrical and optical properties as well as applications of semiconductors have been published by Malik *et al.*,⁶ Ambacher,⁷ Strite *et al.*,⁸ and Jones and O'Brien.⁹ Applications of semiconductors include in solar cells, light emitting diodes, photocathodes, lasers and thermal imaging devices. Volatile organometallic compounds have been increasingly used for the deposition of compound semiconductors. Metalorganic chemical vapour deposition (MOCVD) is commonly used for the formation of semiconductors using organometallic precursors.² This process either uses a dual- or single-source precursor system. The progress of techniques of this type has been the result of developments in precursor chemistry including improved synthesis and purification. One of the driving forces in recent years in the organometallic chemistry of group 13 (Al, Ga, In) has been their increased use in the electronics industry, for example semiconducting III-V materials such as GaAs, GaN and InP. Other semiconductors formed using organometallic precursors include chalcogenides (SnS, In₂S₃), and ternary phases (CuInSe₂). In this section the development of precursors for compound semiconductors for use in AACVD is described.

3.1 Groups 12 and 16 (II-VI) thin films

The intermediate energy band gaps of II-VI semiconductors has led to their use in a variety of devices.¹⁰ For example, cadmium chalcogenides have applications in solid-state solar cells, in light-emitting diodes for flat-panel displays, sensors and in field-effect transistors. The Zn- and Cd-based chalcogenides (ZnS, ZnSe, CdS, CdSe and CdTe) have been grown by conventional MOCVD from dimethyl-cadmium or -zinc in combination with H₂S, H₂Se or Me₂Te¹¹ and from single-source precursors.² Low temperature growth is important because these II-VI materials interdiffuse and form defects at temperatures above 500 °C. To reduce toxicity

and the growth temperature and control the purity of the films deposited new precursors have been developed. For example, mixed alkyl/dithio- or diseleno-carbamates and xanthates^{12–16} are potential precursors to II-VI materials as they provide access to lower deposition temperatures and zinc selenide, cadmium sulfide and cadmium selenide thin films have been deposited from compounds, of the type [RM(E₂CNEt₂)₂]₂ (M = Zn, Cd, E = S, Se, R = Me, CH₂CMe₃)¹⁷ *via* MOCVD. Reviews by Gleizes¹⁸ and O'Brien^{2,19} provide detailed accounts on the use of other single-source precursors for the deposition of chalcogenide materials by MOCVD. Complexes of this type were expected to be relatively unstable and have low volatility. However, a wide range of compounds have been used in AACVD processes to produce II-VI thin films (*vide infra*). Thin films of these materials have also been deposited by other solution based methods such as spray pyrolysis,^{20,21} spin coating,²² electrostatic assisted aerosol jet deposition,²³ chemical bath deposition^{24,25} and solution growth.²⁶


AACVD of CdS, ZnS and Cd_{1-x}Zn_xS films was originally reported by Hampden-Smith *et al.* utilising precursors, of the type [M(SOCMe)₂(tmeda)] (where tmeda = *N,N,N,N*-tetramethylethylenediamine).^{27,28} AACVD was the chosen CVD technique to aid with the delivery of precursors with lower volatility and ease of handling of highly reactive precursors. The zinc compound, [Zn(SOCMe)₂(tmeda)] was prepared *via* reaction of ZnEt₂ with two equivalents of HSOCMe and 1 equivalent of tmeda, whereas the Cd species was isolated from the reaction of Cd(CO₃) with HSOCMe and one equivalent of tmeda. The compounds were found to be monomeric and isostructural in the solid state with both possessing S-bonded thioacetate ligands. The coordination environment of the metal atoms in both compounds was a distorted tetrahedral comprising two nitrogen atoms and two sulfur atoms. Decomposition of the compounds was observed to proceed *via* thermally induced thioacetic anhydride elimination, as shown in eqn (1).



Precursors, [Zn(SOCMe)₂(tmeda)] and [Cd(SOCMe)₂(tmeda)] were used individually to deposit ZnS and CdS films *via* AACVD from toluene solutions at 100–250 °C. AACVD of Cd_{1-x}Zn_xS films at 175 °C was also investigated from mixtures of [Cd(SOCMe)₂(tmeda)] and [Zn(SOCMe)₂(tmeda)] in various Cd : Zn ratios of 6 : 4, 5 : 5, 4 : 6 and 2.5 : 7.5. The deposited films were found to have similar growth rates and morphologies as the individual ZnS and CdS films and adopted a (002)-orientated hexagonal phase. Binary phases of ZnS and CdS were not observed by X-ray diffraction but a general trend was found where the films were Cd deficient compared to the solutions by ~5–10 at%.

More recently, thin films of CdS, ZnS and Cd_{1-x}Zn_xS have been deposited by AACVD using thio- and dithio-biuret zinc and cadmium precursors, of the type [M{(SCNR₂)₂N₂}]₂ (M = Zn, Cd, R = Me, Et) and [M(SON(CNⁱPr)₂)₂]₂ (M = Zn, Cd).^{29,30} The ligands and precursors were synthesised as shown in Scheme 1. Reaction of sodium thiocyanate, *N,N'*-dialkylcarbonyl chloride and the relevant dialkylamine produced the 1,1,5,5-tetraalkyl-2-thiobiuret ligand. The metal complexes were formed by




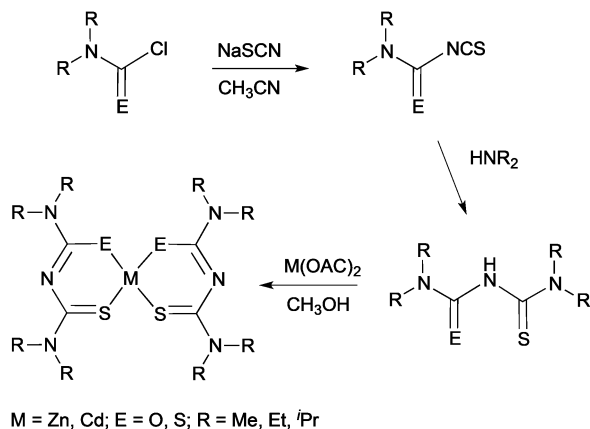

Scheme 1 Synthesis of thio- and dithio-biuret zinc and cadmium precursors.

addition of the corresponding metal acetate in methanol to the ligand. A similar synthetic route was followed to isolate dithio-biuret complexes starting from *N,N'*-dialkylthiocarbamylchloride. Single crystal X-ray diffraction showed that the zinc or cadmium atom in the precursor adopted a distorted tetrahedral geometry. Thermogravimetric analysis (TGA) indicated that the zinc and cadmium precursors decomposed to the corresponding metal sulfides at similar temperatures. AACVD of $[\text{Zn}\{(\text{SCNR}_2)_2\text{N}\}_2]$ ($R = \text{Me, Et}$) and $[\text{Zn}\{\text{SON}(\text{CN}^i\text{Pr}_2)_2\}_2]$ in THF afforded cubic ZnS films with small rods and granular crystallites at 300 and 350 °C but hexagonal ZnS with granular crystallites at 400 and 450 °C. Likewise, the corresponding cadmium precursors resulted in the deposition of hexagonal granular CdS films at all deposition temperatures. By varying the molar ratio of Zn : Cd compounds in the precursor mixture, ternary films of $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ were deposited at 400 °C. The formation of a solid solution was confirmed by powder X-ray diffraction (XRD), energy dispersive X-ray (EDAX) spectroscopy and UV-vis. The optical band gap for the ZnS films was found to be 3.35 eV, for CdS 2.39 eV and for the ternary material $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ ranged from 3.10–2.52 eV depending on the value of x ($x = 0.25, 0.50, 0.75$). In general, the band gap was found to increase with increasing temperature, as expected. Overall, pairs of precursors resulted in the deposition of homogeneous $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ films, which is largely the result of the zinc and cadmium precursors decomposing at similar temperature in a single step. Thio- and dithio-biurets have also been explored for the synthesis of other metal complexes and deposition of materials including Co, Ni, Fe, In, and Cu.^{20,31}

A cadmium complex of dimorpholinodithioacetylacetonate (msacmsac) has been used as a single-source precursor for the deposition of CdS films by AACVD.³² The ligand msacmsac was prepared by the reaction of morpholine with sulfur and allyl propyl ether at 110 °C for several hours. Subsequent reaction of the ligand with cadmium nitrate resulted in the isolation of the cadmium complex, $[\text{Cd}(\text{msacmsac})_2(\text{NO}_3)_2]$. The structure of the complex shows a bidentate coordination by the sulfur atoms of each ligand to the cadmium metal and an overall octahedral coordination geometry, as shown in Fig. 2. AACVD of $[\text{Cd}(\text{msacmsac})_2(\text{NO}_3)_2]$ in dimethylformamide and chloroform (1 : 1)

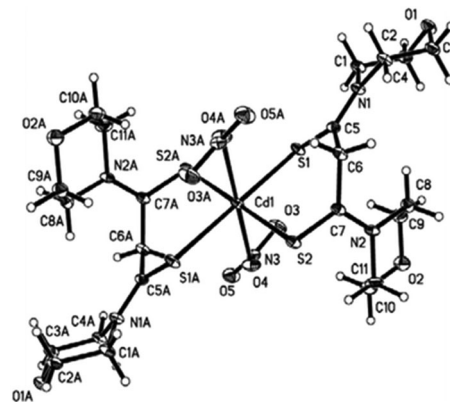

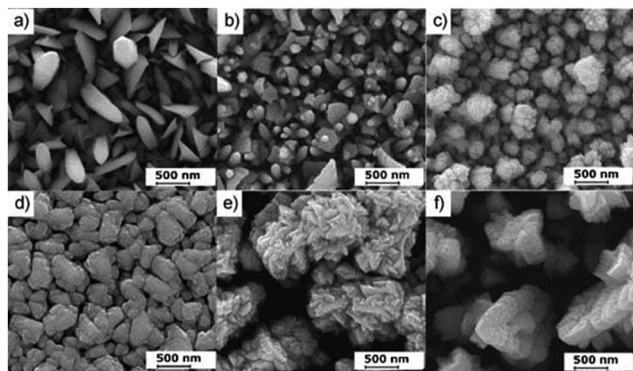


Fig. 3 SEM images of CdS thin films deposited from $[\text{Cd}(\text{S}_2\text{CNCy}_2)_2 \cdot \text{py}]$ on FTO (a–c) and soda glass (d–f) at 350, 400, and 450 °C from THF solution. Reproduced with permission from ref. 37. Copyright 2012 Wiley.

AACVD of the related zinc complexes, $[\text{Zn}(\text{S}_2\text{CNCy}_2)_2 \cdot \text{py}]$ and $[\text{Zn}(\text{S}_2\text{CN}(\text{CH}_2\text{Ph})\text{Me})_2 \cdot \text{py}]$ in toluene at 375, 425 and 475 °C, has also been reported.³⁹ In general, ZnS crystallises into two structural polymorphs, cubic (sphalerite) and hexagonal (wurtzite), and phase selectivity is influenced by the precursor, deposition technique, substrate and processing parameters. Using these precursors in AACVD it was found that at the lower temperature of 375 °C the cubic phase was dominant with the hexagonal phase present as a minority phase. At the higher temperature of 475 °C the hexagonal phase was observed as the major phase with some cubic phase present. SEM showed that the surface morphology of the ZnS films deposited was strongly dependent on the nature of the precursor as well as the deposition temperature. For example, using $[\text{Zn}(\text{S}_2\text{CNCy}_2)_2 \cdot \text{py}]$, films deposited at 375 °C consisted of well-orientated cauliflower-like structures, whereas unstructured particles were formed from $[\text{Zn}(\text{S}_2\text{CN}(\text{CH}_2\text{Ph})\text{Me})_2 \cdot \text{py}]$ at the same temperature. The band gaps of the films deposited at 475 °C from $[\text{Zn}(\text{S}_2\text{CNCy}_2)_2 \cdot \text{py}]$ and $[\text{Zn}(\text{S}_2\text{CN}(\text{CH}_2\text{Ph})\text{Me})_2 \cdot \text{py}]$ were 3.36 and 3.40 eV, respectively corresponding well with that expected for hexagonal ZnS.

Recently, the pyridine adduct of bis(piperidine dithiocarbamate)cadmium(II), $[\text{Cd}(\text{S}_2\text{CNC}_5\text{H}_{10})_2 \cdot \text{py}]$ was evaluated as a single-source precursor for the deposition of CdS films.⁴⁰ AACVD of $[\text{Cd}(\text{S}_2\text{CNC}_5\text{H}_{10})_2 \cdot \text{py}]$ in chloroform at 350–450 °C deposited thin films of hexagonal CdS with band gaps of ~ 2.6 eV. Again the temperature of deposition was found to affect the resulting morphology of the film, as shown in Fig. 4. At the lower temperature of 350 °C the CdS films had regular hexagonal-like domains whereas at 450 °C close to spherical granules were observed. The deposition temperature was observed to modify the grain sizes as well as the surface roughness. These precursors were also used to synthesize CdS nanoparticles.

Thin films of ZnS and CdS have also been deposited from $[\text{M}(\text{S}_2\text{CN}^n\text{Bu}_2)_2]$ ($\text{M} = \text{Zn}, \text{Cd}$) *via* AACVD in toluene at 350–450 °C on soda glass substrates.^{41,42} For ZnS, no deposition was observed at 350 °C but at higher temperatures hexagonal ZnS was deposited with a rod-like structure. Thin films of hexagonal CdS could be deposited at 350 °C, which consisted of densely packed granular crystallites whereas at higher temperatures the morphology changes to a flake-like structure.

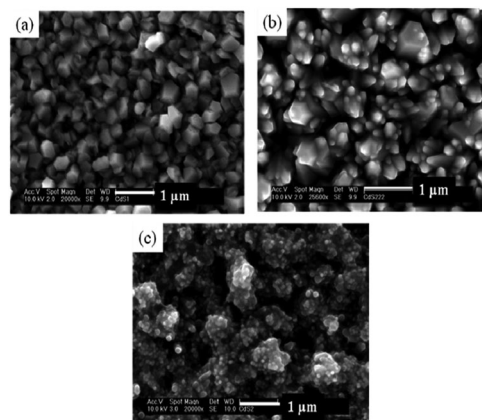


Fig. 4 SEM images of CdS thin films deposited from $[\text{Cd}(\text{S}_2\text{CNC}_5\text{H}_{10})_2 \cdot \text{py}]$ at (a) 350 °C; (b) 400 °C and (c) 450 °C. Reproduced from ref. 40 with permission from the Centre National de la Recherche Scientifique (CNRS) and the Royal Society of Chemistry.

AACVD of CdS and CdTe has been carried out using $[\text{Cd}\{(\text{SP}^i\text{Pr}_2)_2\text{N}\}_2]$ and $[\text{Cd}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ in toluene at substrate temperatures between 550–550 °C and 375–475 °C, respectively.^{43,44} AACVD of $[\text{Cd}\{(\text{SP}^i\text{Pr}_2)_2\text{N}\}_2]$ resulted in the formation of hexagonal CdS at deposition temperatures of 500 °C but growth of cubic Cd_6P_7 and orthorhombic Cd_7P_{10} at 525 °C. SEM of the CdS films grown at 500 °C showed that they were composed of dense, ribbon-like primary crystallites. Synthesis of the CdTe precursor, $[\text{Cd}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ could not be achieved by direct reaction of $\text{NH}(\text{P}^i\text{Pr}_2)_2$ with tellurium. An alternative approach involved metalation of $\text{NH}(\text{P}^i\text{Pr}_2)_2$ with NaH prior to reaction with tellurium, which facilitated the formation of $\text{Na}[\text{N}(\text{TeP}^i\text{Pr}_2)_2]$ which was then reacted with CdCl_2 . AACVD of $[\text{Cd}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ resulted in the formation of a mixture of cubic CdTe and hexagonal Te at 375 °C and pure cubic CdTe films at 475 °C with preferred orientation along (111) direction. Under similar conditions, AACVD of $[\text{Hg}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ resulted in the deposition of hexagonal tellurium, which may be due to reductive elimination of mercury at higher temperatures.⁴¹ Related complexes have also been used to form CuTe, Ag_7Te_4 and AuTe_2 films.⁴⁵

Bis-chelates of cadmium, of the type $[\text{Cd}\{^i\text{Pr}_2\text{P}(\text{X})\text{NC}(\text{Y})\text{NC}_4\text{H}_8\text{--}\eta^2\text{--S}_2\text{O}\}]$ ($\text{X} = \text{S}, \text{Y} = \text{O}; \text{X} = \text{O}, \text{Y} = \text{S}$), have been used as single-source precursors for the deposition of thin films *via* AACVD.⁴⁶ Preliminary AACVD studies at 400 and 500 °C indicated that metal-enriched CdS formed with a high degree of carbon contamination from the precursor containing a $\text{P}=\text{O}$ group.


3.2 Groups 13 and 15 (III–V) thin films

The conventional approach to growing III–V thin films is where separate group III and V precursors are combined. The metalorganic precursors traditionally employed are readily available commercially and have convenient vapour pressures. Manasevit first described the use of organometallic compounds to deposit III–V films in 1968,⁴⁷ and these original precursors are still favoured today. The volatile group III trialkyls, such as trimethylaluminum (AlMe_3), trimethylgallium (GaMe_3), and trimethylindium (InMe_3) in combination



The deposition of high quality polycrystalline GaAs thin films on glass substrates was reported utilizing the single-source precursor, $[\text{Me}_2\text{GaAs}(\text{H})^t\text{Bu}]_2$.⁵⁴ The precursor was synthesised from the reaction of GaMe_3 and $^t\text{BuAsH}_2$ in a 1 to 1.5 ratio in

An alternative arsenic precursor to AsH_3 includes the liquid precursor, tris(dimethylaminoarsine), $\text{As}(\text{NMe}_2)_3$,^{44,55} which has been used in MOCVD techniques since the compound is lacking direct As-C bonds, reducing any potential carbon contamination in resulting films and it possesses a low relative decomposition temperature.⁶⁴ The main decomposition products of $\text{As}(\text{NMe}_2)_3$ have been shown to include dimethylamine, hydrogen and aziridine.⁶⁵ The deposition of polycrystalline GaAs thin films on glass substrates from the AACVD of a one-pot solution of the commercially available precursors, $\text{As}(\text{NMe}_2)_3$ and GaMe_3 , in toluene has been described.⁵⁵ The resulting GaAs films were stoichiometric when a 1.5 to 1 ratio of $\text{As}(\text{NMe}_2)_3$ and GaMe_3 was used in the AACVD solution. The films were relatively low in carbon and oxygen contaminations as shown by cross sectional EDA X mapping. The films were shown to have a structured morphology due to the high CVD growth rate, as shown by the SEM micrographs in Fig. 5.



Access to unusual or metastable phases using single-source precursors are possible either because of kinetic control of a metastable phase or because of entry into an unusual part of a phase diagram since lower deposition temperatures are often associated with the use of such precursors. Controlling the deposited phase by the molecular design of the precursor has been investigated in the CVD of gallium and indium chalcogenides.⁶⁶ The III–VI compounds are semiconductors which find application in photocatalysis, optoelectronic and photovoltaic devices.⁶⁷ For example, solar cells based on indium sulfide, β - In_2S_3 , have shown a power conversion efficiency of 16.4%, comparable to the more toxic CdS based solar devices.⁶⁸ They also have a potential application as passivating layers for III–V devices and are related to ternary phases, such as CuInE_2


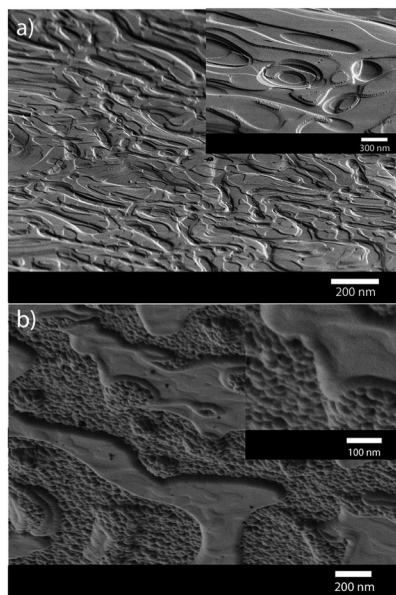


Fig. 5 SEM images of crystalline GaAs films grown *via* AACVD from $\text{As}(\text{NMe}_2)_3$ and GaMe_3 at (a) 500 °C and (b) 550 °C. Reproduced from ref. 63 with permission from The Royal Society of Chemistry.

(E = S or Se) with uses in solar cells.⁶⁹ Gallium sulfide can exist as a solid with several structural types and compositions. The wurtzite-type hexagonal structures, $\alpha\text{-Ga}_2\text{S}_3$ and $\beta\text{-Ga}_2\text{S}_3$, as well as a monoclinic $\gamma\text{-Ga}_2\text{S}_3$ phase exists. The subvalent gallium sulfide (GaS) exists as a hexagonal layered structure. A range of techniques have been used to deposit III–VI thin films including solvothermal,⁷⁰ spray ion layer gas reaction,⁷¹ electrostatic spray assisted vapour deposition⁷² and low pressure CVD.^{73,74} Examples of precursors to metal chalcogenides have been reviewed.⁷⁵ Mixed alkyl/dithio or diselenocarbamates of gallium and indium can act as precursors to III–VI materials.^{76,77} Compounds of general formula $[\text{R}_2\text{M}(\text{S}_2\text{CNR}'_2)]$ (M = Ga: $\text{R}' = \text{Et}$, R = Me, Et, CH_2CMe_3 ; R = $t\text{Bu}$, $\text{R}' = \text{Me}$, Et, $n\text{Pr}$; M = In, $\text{R}' = \text{Et}$, R = Me, Et, CH_2CMe_3) have been synthesised and they range from liquids (M = Ga) to low melting solids (M = In). Gallium sulfide (GaS) films have been grown by MOCVD whereas thin films of various phases of In_xS_y were grown by low pressure CVD.

Thin films of $\alpha\text{-Ga}_2\text{S}_3$ have been deposited by AACVD from $[\text{GaMe}(\text{SCOMe})_2(\text{dmpy})]$ (dmpy = 3,5-dimethylpyridine).⁷⁸ The decomposition of the precursor shows two distinct steps of mass loss. The first step corresponds to the loss of dmpy and thioacetic acid and the second to the loss of acetone, as shown in Scheme 2. On heating the related compound, $[\text{Ga}(\text{SCOMe})_3(\text{dmpy})]$, the elimination of thioacetic anhydride was observed. At relatively low temperatures of 275–310 °C, uniform crystalline Ga_2S_3 films were obtained from both compounds with no evidence of impurities from carbon or oxygen. AACVD of a related mixed-metal thiocarboxylate compound, $[(\text{Ph}_3\text{P})\text{Cu}(\text{SCOPh})_3\text{In}(\text{SCOPh})]$ in THF at 350–450 °C resulted in the formation of $\beta\text{-In}_2\text{S}_3$ rather than the expected CuInS_2 most likely due to dissociation of the compound in solution.⁷⁹ In contrast, the Ag compound $[(\text{Ph}_3\text{P})_2\text{AgIn}(\text{SCOR})_4]$ (R = Me, Ph) did produce AgIn_5S_8 films *via* AACVD.

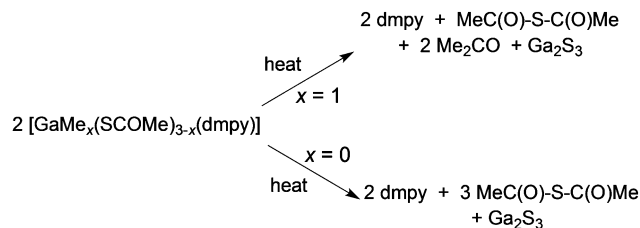

Scheme 2 Decomposition of $[\text{GaMe}(\text{SCOMe})_2(\text{dmpy})]$ and $[\text{Ga}(\text{SCOMe})_3(\text{dmpy})]$.

An alternative class of single-source precursors based on the bidentate bis(diisopropylselenophosphoryl)amide ligand, $[\text{NH}(\text{SeP}^i\text{Pr}_2)_2]$ have been used to deposit III–VI materials.⁸⁰ The compounds $[\text{R}_2\text{M}(\text{SeP}^i\text{Pr}_2)_2\text{N}]$ (M = Ga, R = Me; M = In, R = Me, Et) were synthesised from the reaction of MR_3 with $\text{NH}(\text{SeP}^i\text{Pr}_2)_2$. Thin films of cubic- Ga_2Se_3 were grown from the gallium precursor in toluene by AACVD at 450 and 475 °C. Similarly, thin films of hexagonal $\gamma\text{-In}_2\text{Se}_3$ were deposited from the methyl indium derivative. The related compound $[\text{In}\{(\text{SP}^i\text{Pr}_2)_2\text{N}\}_2\text{Cl}]$ was shown to deposit polycrystalline tetragonal $\beta\text{-In}_2\text{S}_3$ films *via* AACVD.⁸¹

The indium and copper precursors, $[\text{In}(\text{S}_2\text{P}^i\text{Bu}_2)_3]$ and $[\text{Cu}(\text{S}_2\text{P}^i\text{Bu}_2)(\text{PPh}_3)_2]$ have been synthesised *via* reaction of the metal chloride with sodium diisobutylidithiophosphinate and used as single-source precursors.⁸² The air and moisture stable indium compound $[\text{In}(\text{S}_2\text{P}^i\text{Bu}_2)_3]$ deposited thin films of cubic In_2S_3 on glass substrates by AACVD at 350–500 °C. Powder XRD showed that monophasic cubic In_2S_3 was deposited at all temperatures, as shown in Fig. 6. As expected, improved crystallinity was observed as the deposition temperature increased. When used in combination with the copper complex, thin films of CuInS_2 were deposited by using a 1 : 1 molar ratio of $[\text{In}(\text{S}_2\text{P}^i\text{Bu}_2)_3]$ and $[\text{Cu}(\text{S}_2\text{P}^i\text{Bu}_2)(\text{PPh}_3)_2]$. The deposited In_2S_3 and CuInS_2 thin films showed good coverage over the entire substrate and good crystallinity and hence may be suitable as a photoabsorber in solar devices. Similarly, CuInSe_2 , CuGaSe_2 and $\text{CuIn}_{0.7}\text{Ga}_{0.3}\text{Se}_2$ thin films have been deposited on glass substrates using the related $[\text{M}_x(\text{Se}_2\text{P}^i\text{Pr}_2)_y]$ precursors (M = Ga, In, Cu) at 300–350 °C.⁸³ AACVD of the indium precursor $[\text{In}(\text{Se}_2\text{P}^i\text{Pr}_2)_3]$ at 300–500 °C in toluene yielded thin films of indium selenide in the γ -phase of In_2Se_3 at all temperatures. The best films were deposited at 450 °C and SEM showed uniform coverage with highly crystalline grains deposited. Different morphologies of the grains were obtained at the different deposition temperatures, as shown in Fig. 7.

The complexes, $[\text{Ga}(\mu\text{-Te})\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_3]$ and $[\text{In}(\mu\text{-Te})\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_3]$ were synthesised as shown in Scheme 3 and used as precursors in an AACVD process due to their low volatility.⁸⁴ The gallium precursor resulted in the deposition of a mixture of cubic Ga_2Te_3 , monoclinic GaTe and hexagonal Te at 425–475 °C. The formation of elemental tellurium is most likely to be due to decomposition of the precursor. Pure cubic In_2Te_3 films were deposited by AACVD of the indium precursor at 375–475 °C. The films were shown to be rough and granular by SEM, which is generally associated with the delivery of precursors as droplets and a homogeneous reaction contribution during the AACVD process.



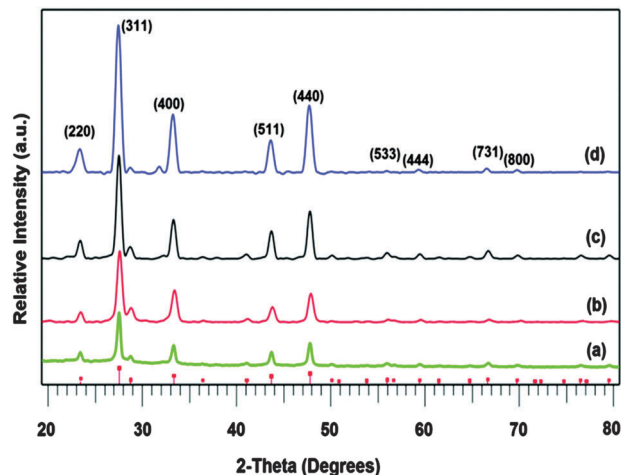


Fig. 6 p-XRD patterns of as deposited In_2S_3 thin films from $[\text{In}(\text{S}_2\text{P}^i\text{Bu}_2)_3]$ precursor at temperatures (a) 350 °C, (b) 400 °C, (c) 450 °C and (d) 500 °C. Vertical lines below show the standard ICDD pattern 01-084-1385 for In_2S_3 . Reproduced from ref. 82 with permission from the Centre National de la Recherche Scientifique (CNRS) and the Royal Society of Chemistry.


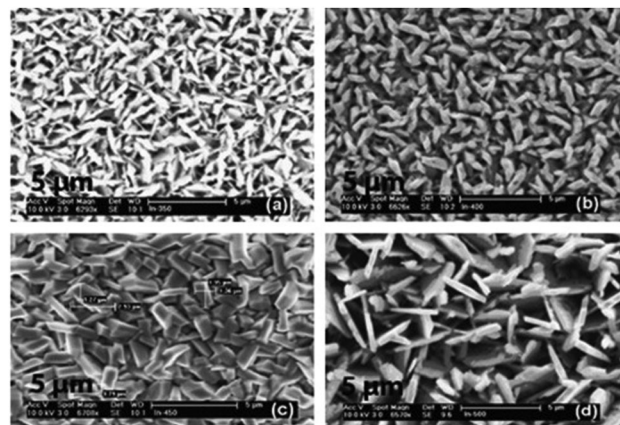



Fig. 7 SEM images of the In_2Se_3 films deposited from $[\text{In}(\text{Se}_2\text{P}^i\text{Pr}_2)_3]$ at (a) 300 °C, (b) 350 °C, (c) 400 °C and (d) 450 °C. Reproduced with permission from ref. 83. Copyright 2014 Elsevier.

Dithiocarbamate complexes have also been used as precursors to III–VI thin films in AACVD processes. Indium dithiocarbamates, of the type $[\text{In}(\text{S}_2\text{CNRR}')_3 \cdot n(\text{py})]$ (where py = pyridine, $\text{R} = \text{R}' = \text{Cy}$, $n = 2$; $\text{R} = \text{R}' = {}^n\text{Pr}$, $n = 1.5$; $\text{NRR}' = \text{Pip}$, $n = 0.5$; $\text{R} = \text{Bz}$, $\text{R}' = \text{Me}$, $n = 0$)⁸⁵ were synthesised by the metathetical reaction of sodium dithiocarbamate and indium trichloride in methanol/pyridine solutions, as shown in eqn (3). Typically addition of a Lewis base yields precursors with enhanced volatility, facile decomposition and sometimes air stability. For these indium complexes, the pyridine did not coordinate to the metal centre but it was present as solvate molecules in the crystal lattices of three of the compounds and the compounds were found to be air and moisture stable. AACVD using the $[\text{In}(\text{S}_2\text{CNRR}')_3 \cdot n(\text{py})]$ precursors in toluene at 300–450 °C resulted in the deposition of tetragonal $\beta\text{-In}_2\text{S}_3$ thin films. The morphology of the resulting films were shown by SEM to vary with rise in substrate temperature, as shown in

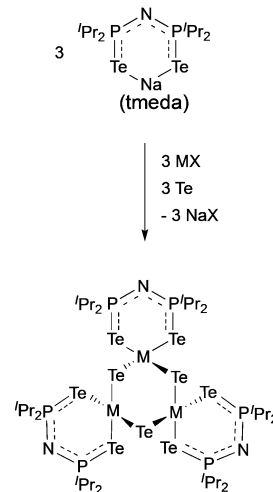

Scheme 3 General synthesis of $[\text{Ga}(\mu\text{-Te})\{\text{N}(\text{TeP}^i\text{Pr}_2)_2\}_3]$ ($\text{M} = \text{Ga}$, $\text{X} = \text{I}$) and $[\text{In}(\mu\text{-Te})\{\text{N}(\text{TeP}^i\text{Pr}_2)_2\}_3]$ ($\text{M} = \text{In}$, $\text{X} = \text{Cl}$).

Fig. 8, with granular crystallites, multi-shaped interconnected crystallites and agglomerates of particles forming. UV-vis measurements of the $\beta\text{-In}_2\text{S}_3$ films showed band gap energies of 2.2 eV. Films deposited from $[\text{In}(\text{S}_2\text{CNCy}_2)_3] \cdot 2\text{py}$ were shown to be promising for application in solar cells (*vide infra*). Thin films of CuInS_2 , CuInSe_2 and CuGaSe_2 have also been grown *via* AACVD using the precursors $[\text{M}(\text{E}_2\text{CNMe}^n\text{Hex})_3]$ ($\text{E} = \text{S}, \text{Se}$; $\text{M} = \text{Ga}, \text{In}$) and $[\text{Cu}(\text{E}_2\text{CNMe}^n\text{Hex})_3]$.⁸⁶



3.4 Groups 14 and 16 (IV–VI) thin films

Tin sulfide is a IV–VI semiconductor which has three main phases: (i) SnS_2 , (ii) SnS and (iii) Sn_2S_3 which is a mixed $\text{Sn(II)}/\text{Sn(IV)}$ compound.⁸⁷ The band gaps of SnS , SnS_2 and Sn_2S_3 are 1.3 eV, 2.18 eV and 0.95 eV respectively, and all three forms exhibit semiconducting properties. SnS has attracted a lot of attention due to its band gap, which lies between that of GaAs and silicon and depending on the tin content, SnS can be a p-type or n-type conductor. Thin films of tin(II) and tin(IV) sulfides have been investigated as semiconductors, solar collectors and photovoltaic materials. A range of methods have been used to deposit thin films of tin sulfide including spray deposition,⁸⁸ chemical bath deposition,⁸⁹ atomic layer deposition⁹⁰ and dip deposition.⁹¹ A recent review by Lewis *et al.* outlines a range of methods for the deposition of thin films of binary tin chalcogenides, tin sulfide (SnS), selenide (SnSe) and telluride (SnTe), as well as describing methods to make their nanocrystalline analogues.⁹²

Tin sulfide films have been grown from single-source thiolate precursors by AACVD.^{93,94} The precursor, $[\text{Sn}(\text{SCH}_2\text{CH}_2\text{S})_2]$ was prepared from the reaction of ethane-1,2-dithiol, 2 equiv. of ${}^n\text{BuLi}$ and SnCl_4 . AACVD of $[\text{Sn}(\text{SCH}_2\text{CH}_2\text{S})_2]$ in acetone in the presence of H_2S at 350–550 °C resulted in the deposition thin films of tin sulfides. The deposition temperature dictated



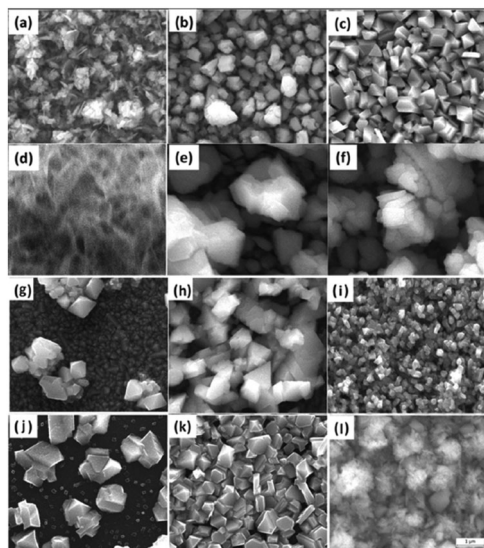


Fig. 8 SEM images of β - In_2S_3 films deposited using the precursors $[\text{In}(\text{S}_2\text{CNCy}_2)_3] \cdot 2\text{py}$ at (a) 300 °C, (b) 350 °C and (c) 400 °C; $[\text{In}(\text{S}_2\text{CN}(\text{Pr})_2)_3] \cdot 1.5\text{py}$ at (d) 300 °C, (e) 350 °C and (f) 400 °C; $[\text{In}(\text{S}_2\text{CNip})_3] \cdot 0.5\text{py}$ at (g) 300 °C (h), 350 °C and (i) 400 °C and $[\text{In}(\text{S}_2\text{CNBzMe})_3]$ at (j) 300 °C, (k) 350 °C and (l) 400 °C. Reproduced from ref. 85 with permission from The Royal Society of Chemistry.

which phase of tin sulfide was deposited; SnS_2 at 350 °C, Sn_2S_3 at 400 °C and SnS at 500 °C and above. The use of AACVD as the deposition technique was necessary as the precursor was involatile and had poor carry over under atmospheric pressure CVD conditions. AACVD of $[\text{Sn}(\text{SCH}_2\text{CH}_2\text{S})_2]$ without the use of H_2S also resulted in the formation of tin sulfide films with SnS and a trace of Sn_2S_3 formed at 400 °C and at 500 °C and above single phase SnS . No films were deposited at 350 °C or below. AACVD of the tin monothiolate compound, $[\text{Sn}(\text{SPh})_4]$ was shown to decompose by disulfide (RS-SR) elimination to leave reactive tin metal, which was readily oxidized to Sn_3O_4 in the absence of added H_2S . In general, $[\text{M}(\text{SR})_4]$ molecules have significant distortion from tetrahedral geometry due to non-covalently bonded $\text{S} \cdots \text{S}$ interactions which promotes the disulfide elimination pathway. The use of a chelating bis-thiolate in $[\text{Sn}(\text{SCH}_2\text{CH}_2\text{S})_2]$ eliminates the possibility of this occurring, hence it can successfully act as a single-source precursor for tin sulfide films. AACVD of $[\text{Sn}(\text{SPh})_4]$ with H_2S added as a co-reactant did yield tin sulfide films with the film deposited at 450 °C consisting of mainly SnS_2 while at 500 °C SnS was the dominant component.

Other single-source precursors that have been used in AACVD of tin sulfides include $[\text{Bz}_3\text{SnCl}(\text{L})]$ (L = thiosemicarbazones of 4-chlorobenzaldehyde and salicylaldehyde, Bz = benzyl) in toluene at 270–370 °C to deposit $\text{SnS}^{95,96}$ and a range of dithiocarbamate complexes have also been investigated.^{97,98} Unsymmetrical tin(II) dithiocarbamates, of the type $[\text{Sn}(\text{S}_2\text{CNRR}')_2]$ (R = Et, R' = ⁿBu or Et; R = Me, R' = ⁿBu) were synthesised either by direct reaction of the sodium salt of the dithiocarbamate with SnCl_2 or *via* reaction of CS_2 with a secondary amine in the presence of a base followed by metathesis of SnCl_2 . AACVD of $[\text{Sn}(\text{S}_2\text{CNRR}')_2]$ was carried out in THF at 450 and 500 °C. SnS was deposited with some contamination

from SnO_2 and the effect of concentration of the precursor solution was studied. The use of higher concentrations of precursors was found to be key for the formation of stoichiometric or near-to-stoichiometric films of SnS for all precursors studied, as shown in Fig. 9. A direct band gap of 1.2 eV was estimated for the films and the morphology was shown by SEM to consist of bundles of sheets comprised of small crystallites.

A series of related organotin dithiocarbamates, $[\text{Sn}(\text{C}_4\text{H}_9)_2 \cdot (\text{S}_2\text{CNRR}')_2]$ ($\text{R} = \text{Et}$, $\text{R}' = \text{Et}$, Me , ^nBu ; $\text{R} = \text{Me}$, $\text{R}' = \text{hexyl}$) were synthesised *via* the reaction of $^n\text{BuSnCl}_2$ with the sodium salt of the dithiocarbamate.⁹⁷ The compounds, $[\text{Sn}(\text{C}_4\text{H}_9)_2(\text{S}_2\text{CNMe}^n\text{Bu})_2]$ and $[\text{Sn}(\text{C}_4\text{H}_9)_2(\text{S}_2\text{CN}^n\text{Bu})_2]$ were characterised by single crystal X-ray diffraction which showed that the tin has four covalent bonds (2C and 2S) in a distorted tetrahedral geometry. A weaker bonding interaction with tin along the tetrahedral face occurs from the other S atom on each dithiocarbamate ligand, as shown in Fig. 10. Therefore there are two types of Sn-S bonds, one shorter covalent Sn-S bond ($\sim 2.526 \text{ \AA}$) and a longer weaker Sn-S bond ($\sim 2.940 \text{ \AA}$). AACVD of $[\text{Sn}(\text{C}_4\text{H}_9)_2 \cdot (\text{S}_2\text{CNRR}')_2]$ ($\text{R} = \text{Et}$, $\text{R}' = \text{Et}$, Me , ^nBu ; $\text{R} = \text{Me}$, $\text{R}' = \text{hexyl}$) in toluene at $400\text{--}530^\circ\text{C}$ resulted in the deposition of tin sulfide thin films. No deposition occurred at substrate temperatures below 400°C . All the compounds primarily deposited SnS , however the presence of some SnO_2 was detected by powder XRD. Hall effect measurements indicated that all the films were p-type semiconductors, which is believed to originate from high concentration of Sn vacancy sites. Band gaps varied from 1.2 to 1.7 eV for the films and the highest photosensitivity (2.1%) was obtained from deposition carried out at 500°C using $[\text{Sn}(\text{C}_4\text{H}_9)_2(\text{S}_2\text{CNMe}^n\text{Bu})_2]$. Compounds of this type have also been used to deposit thin films of $\text{Cu}_2(\text{Zn}_y\text{Fe}_{1-y})\text{SnS}_4$ (CZFTS) *via* AACVD in combination with Cu, Fe and Zn dithiocarbamate complexes.⁹⁹

Thin films of SnSe have been deposited by AACVD using either $[\text{Sn}(\text{Se}_2\text{PPh}_2)_2]^{100}$ or $[\text{tBu}_2\text{Sn}(2\text{-SeC}_5\text{H}_4\text{N})_2]$ in THF and

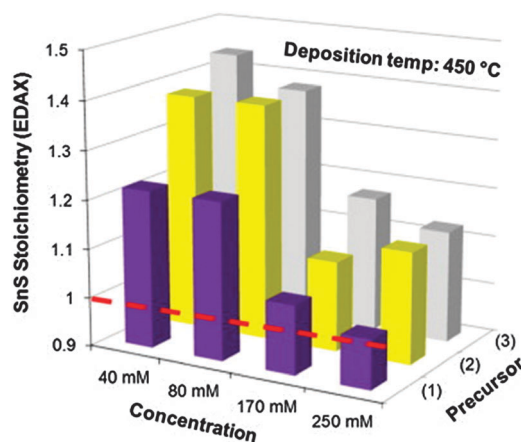


Fig. 9 The effect of concentration of precursors where (1) is $[\text{Sn}(\text{S}_2\text{CNET}^t\text{Bu})_2]$, (2) is $[\text{Sn}(\text{S}_2\text{CNET}^t\text{Bu})_2]$ and (3) is $[\text{Sn}(\text{S}_2\text{CNET}_2)_2]$ on the stoichiometry (%Sn divided by %S found experimentally by EDAX) of SnS films deposited at 450 °C by AACVD. The dashed line indicates an ideal 1 : 1 Sn : S stoichiometry *i.e.* SnS. Reproduced with permission from ref. 98. Copyright 2014 Elsevier.

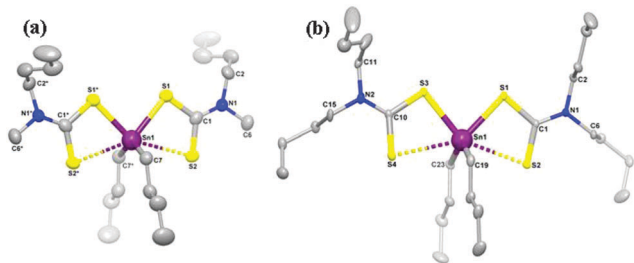


Fig. 10 Molecular structures of (a) $[\text{Sn}(\text{C}_4\text{H}_9)_2(\text{S}_2\text{CNMe}'\text{Bu})_2]$ and (b) $[\text{Sn}(\text{C}_4\text{H}_9)_2(\text{S}_2\text{CN}'\text{Bu})_2]$ with 50% ellipsoidal probability level. All the H atoms on carbon frames are removed for clarity. Reproduced with permission from ref. 97. Copyright 2014 American Chemical Society.

toluene, respectively.¹⁰¹ The temperature of deposition varied depending on the precursor used with SnSe films resulting from film growth at 350–400 °C from $[\text{Sn}(\text{Se}_2\text{PPh}_2)_2]$, whereas higher temperatures of 490–530 °C were necessary to yield SnSe films from $[\text{Bu}_2\text{Sn}(2\text{-SeC}_5\text{H}_4\text{N})_2]$. When the single-source precursor, $[\text{Sn}(\text{Se}_2\text{PPh}_2)_2]$ was used in combination with $[\text{Cu}(\text{acac})_2]$, copper tin selenide (Cu_2SnSe_3) thin films were deposited on glass substrates which could have potential applications in optoelectronics and photovoltaics.

Dithiocarbamates have also been used to deposit thin films of PbS.^{102,103} Lead chalcogenides are narrow band gap semiconductors with band gaps of 0.41 and 0.27 eV for PbS and PbSe, respectively and find application in high performance photoconductive infrared detectors. AACVD of the precursors $[\text{Pb}(\text{S}_2\text{CNRR}')_2]$ ($\text{R} = \text{Me}$, $\text{R}' = \text{benzyl}$, heptyl, octadecyl; $\text{R} = \text{R}' = \text{dioctyl}$ or Et) in toluene at 350–525 °C on glass substrates deposited grey/black films of PbS. The morphology of the resulting films changed with deposition temperature, as shown in Fig. 11 for $[\text{Pb}(\text{S}_2\text{CNMeBenzyl})_2]$. Deposition at higher temperatures was observed to produce thinner films with much larger and more uniform flakes of average size 8 μm . The minimum temperature required for deposition of PbS thin films from these complexes varied between 350 and 375 °C. These deposition temperatures are lower than those reported for the deposition of PbS thin films from $[\text{Pb}(\text{S}_2\text{CNET}^t\text{Pr})_2]$ and $[\text{Pb}(\text{S}_2\text{CNMe}^n\text{Bu})_2]$.⁹⁴ The difference in the minimum deposition temperature seems to be related to the chain lengths of the alkyl groups on the dithiocarbamate ligand. The longer chain lengths of alkyl groups lower the deposition temperature and appeared to improve the quality of film produced resulting in more uniform and crystalline depositions.

The lead xanthate complex, $[\text{Pb}(\text{S}_2\text{COEt})_2\text{-tmeda}]$ was used as a precursor to deposit PbS films.¹⁰⁴ The structure of the precursor was shown by single crystal X-ray diffraction to be seven-coordinate at lead through three chelating ligands and one weak intermolecular $\text{Pb}\cdots\text{S}$ interaction, as shown in Fig. 12. AACVD of $[\text{Pb}(\text{S}_2\text{COEt})_2\text{-tmeda}]$ in THF at 200 °C resulted in the deposition of cubic PbS thin films with good surface coverage. The films were featureless, highly reflective and pinhole-free regardless of the substrate used. The deposition of PbS thin films on polyimide (Kapton) substrates by AACVD using the related compound $[\text{Pb}(\text{S}_2\text{COBu})_2]$ at temperatures as low as 150 °C

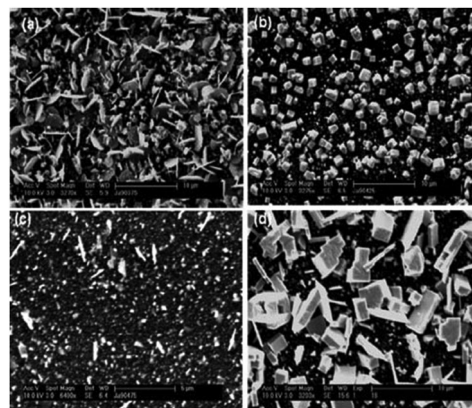


Fig. 11 SEM of PbS thin films deposited from $[\text{Pb}(\text{S}_2\text{CNMeBenzyl})_2]$. At (a) 375 °C, (b) 425 °C, (c) 475 °C and (d) 525 °C. Reproduced from ref. 102 with permission from The Royal Society of Chemistry.

has also been reported.¹⁰⁵ The butyl xanthate was chosen as the thermal stability of the ligand was found to increase with the chain length of the alkyl substituent.

Thin films of PbSe and PbTe have been deposited *via* AACVD using the precursors $[\text{Pb}(4\text{-NO}_2\text{C}_6\text{H}_4\text{CONHCSeN}^i\text{Bu})_2]$ and $[\text{Pb}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ in toluene and THF/ CH_2Cl_2 , respectively.^{106,107} The PbSe films were grown at 250–500 °C and powder XRD showed that the cubic form of PbSe had formed at all temperatures. The films were highly textured along the (200) plane and a range of morphologies resulted which changed depending on the temperature of deposition. The morphology changed from globular crystallites to a disordered network of wires from low to high temperature. AACVD of $[\text{Pb}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_2]$ below 475 °C resulted in films composed of PbTe and Te, but at 475 °C phase-pure cubic PbTe films were deposited. The surface coverage was poor and significant amounts of precursor remained in the precursor solution flask at the end of the AACVD depositions due to the poor solubility of the precursor. Films of PbTe with improved phase purity were obtained by using a hot-injection process.

3.5 Groups 15 and 16 (V–VI) thin films

Binary metal chalcogenides incorporating group 15 and 16 elements, of the type $\text{M}_2\text{V}\text{E}_3$ ($\text{M} = \text{As}$, Sb , Bi ; $\text{E} = \text{S}$, Se , Te)



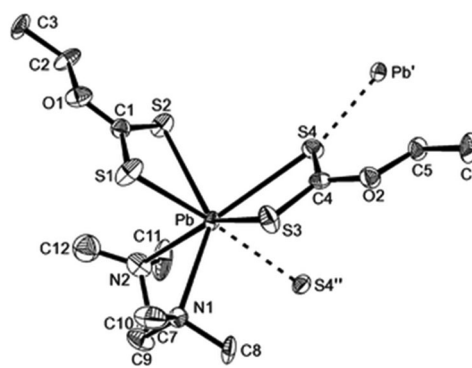


Fig. 12 The asymmetric unit of $[\text{Pb}(\text{S}_2\text{COEt})_2\text{-tmeda}]$ showing the labeling scheme used; thermal ellipsoids are at the 40% level. Reproduced from ref. 104 with permission from The Royal Society of Chemistry.



AACVD of the bismuth dithiocarbamate, $[\text{Bi}(\text{S}_2\text{CNET}_2)_3]_2$ using a range of solvents – chloroform, dichloromethane or a 1 : 1 mixture of chloroform and toluene at 350–450 °C has been reported.¹¹⁴ The precursor was prepared from the reaction of potassium dithiocarbamate with $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ in acetone. As described above, the solvent plays a significant role in determining the morphology and texture of the resulting film. In this study both polar and non-polar solvents were investigated since the polarity and specific heat capacity of the solvent are important during the decomposition process and the droplet size of the aerosol as well as the viscosity of the deposition solution can all be effected. Thin films of Bi_2S_3 in its orthorhombic stibnite type modification were deposited on FTO coated glass. Films deposited using dichloromethane as the solvent were found to have similar morphology to films deposited from chloroform. SEM images of films deposited from chloroform are shown in Fig. 13, which revealed that the films had complex nanostructures composed of nanotubes grown vertically on the substrate. Films grown from a mixture of chloroform and toluene (1 : 1) had a compact nanostructure morphology at 400 °C and a more porous structure at 450 °C, as depicted in Fig. 14. The different morphologies observed was explained by the different solvents leading to homogeneous or heterogeneous deposition reactions. During CVD decomposition of the precursor in the gas phase is termed ‘homogeneous’ whilst decomposition on the heated substrate is ‘heterogeneous’, the ratio between these two processes are directly responsible for a number of characteristics. Chloroform facilitates homogeneous reaction during deposition by evaporating and leaving the precursor molecule to vaporise in the heated zone as it is a low specific heat capacity solvent. The homogeneous reaction results in decomposition of the precursor starting in the gaseous phase, after vaporisation, which is followed by nucleation to form Bi_2S_3 particles. These particles can then be adsorbed onto the substrate surface and a ripening/growing process results in the formation of the nanotubes. However, with addition of toluene, a high specific heat capacity solvent, the vaporisation temperature of the aerosol droplets is increased and heterogeneous reaction is promoted. This means that the vaporised precursor and its gaseous intermediate species are adsorbed onto the surface of the heated substrate where they undergo decomposition and chemical reactions to produce the Bi_2S_3 thin film. The formation of porous Bi_2S_3 thin films at 450 °C from toluene/chloroform mixtures is due to a combination of

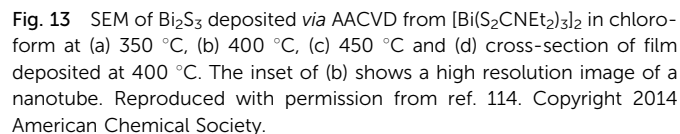

Thin films of rhombohedral Bi_2Se_3 and orthorhombic Bi_2S_3 have been deposited on glass substrates from the precursors $[\text{Bi}\{(\text{SeP}^i\text{Pr}_2)_2\text{N}\}_3]$ and $[\text{Bi}\{(\text{SPR}_2)_2\text{N}\}_3]$ ($\text{R} = {}^i\text{Pr}, \text{Ph}$), respectively, *via* AACVD.¹¹⁶ The films were deposited at 400–475 °C using

THF as the solvent. Films were also deposited using these precursors in a low pressure MOCVD process which was found to yield higher quality films than those deposited by AACVD since no detectable phosphorus contamination was observed and the elemental composition were in better agreement with the stoichiometry expected, in contrast to AACVD films which showed some phosphorus contamination and the formation of bismuth rich films. However, a range of different morphologies were obtained using AACVD.

The related antimony telluride precursor, $[\text{Sb}\{(\text{TeP}^i\text{Pr}_2)_2\text{N}\}_3]$, dissolved in toluene, was used to deposit pure Sb_2Te_3 films using the AACVD process at 375–475 °C.¹¹⁷ TGA indicated that the precursor decomposed by two decomposition steps. The first weight-loss corresponded to the loss of one ligand moiety, $[(\text{TeP}^i\text{Pr}_2)_2\text{N}]$, at 280 °C and the second step occurred at 325 °C resulting in weight loss suggesting formation of Sb_2Te_3 by further fragmentation. Therefore, the deposition studies were carried out at 325–475 °C which showed that 325 °C was too low to initiate deposition. Between 375 and 475 °C black reflective films of rhombohedral Sb_2Te_3 were deposited and SEM showed the formation of randomly orientated plates. Four point probe measurements of the films grown at 475 °C indicated conductivity values between 159 and 180 $\Omega^{-1} \text{cm}^{-1}$.

A number of precursors have also been used to deposit thin films of antimony sulfide in AACVD processes. Thin films of Sb_2S_3 have been deposited from $[\text{Sb}(\text{S}_2\text{COR})_3]$ ($\text{R} = \text{Me}, \text{Et}, ^i\text{Pr}$)¹¹⁸ which were shown to be superior precursors compared to the related antimony dithiocarbamates, $[\text{Sb}(\text{S}_2\text{CNRR}')_3]$,¹¹⁹ which produced Sb_2S_3 films prone to oxidation. The antimony xanthate are less thermally robust than the dithiocarbamates and decomposition of $[\text{Sb}(\text{S}_2\text{COR})_3]$ was suggested to follow a metal-based variation on the Chugaev elimination, as shown in Scheme 4, where xanthates (MS_2COR) are converted to alkene (RH), OCS and MSH. Powder XRD of the resulting films showed the formation of orthorhombic stibnite Sb_2S_3 with a minor component of $\text{Sb}_{10}\text{S}_{15}$, a monoclinic variant of Sb_2S_3 . The morphology of the resulting films was shown to change depending on the precursor used.

Antimony thiosemicarbazones, of the type $[\text{SbCl}_3(\text{L})]$ ($\text{L} =$ thiosemicarbazones of thiopene-2-carboxaldehyde and cinnamaldehyde), as shown below in Fig. 15 have been used to deposit polycrystalline thin films of Sb_2S_3 at 320 °C in acetone.¹²⁰ A rod-shaped morphology was obtained where rods of different

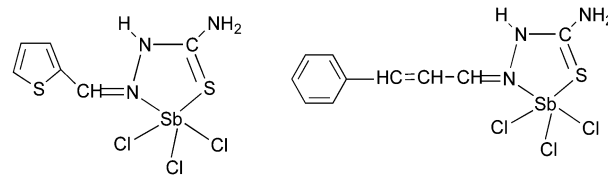


Fig. 15 Structure of $[\text{SbCl}_3(\text{L})]$ ($\text{L} =$ thiosemicarbazones of thiopene-2-carboxaldehyde and cinnamaldehyde).


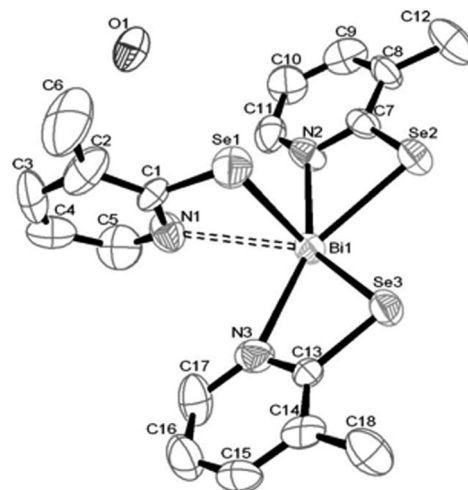


Fig. 16 Crystal structure of $[\text{Bi}\{\text{Se}-\text{C}_5\text{H}_3(\text{Me}-3)\text{N}\}_3] \cdot 0.5\text{H}_2\text{O}$ with atomic number scheme. Reproduced from ref. 121 with permission from The Royal Society of Chemistry.

dimensions had grown in various directions. The optical band gap for the films was found to be 3.48 eV. Thin films of antimony selenide and bismuth selenide have been grown using 2-pyridyl selenolates, of the type $[\text{M}\{\text{Se}-\text{C}_5\text{H}_3(\text{Me}-3)\text{N}\}_3]$ ($\text{M} = \text{Sb}, \text{Bi}$), in an AACVD process.¹²¹ The structure of the bismuth precursor is shown in Fig. 16. Bismuth selenide films, corresponding to rhombohedral Bi_2Se_3 , hexagonal Bi_2Se_3 , hexagonal BiSe were obtained from the bismuth compound depending on the duration and temperature of the depositions whereas Sb_2Se_3 was deposited using the antimony precursor.

4 Main group TCOs

Section 3 described the AACVD of main group semiconductors whereas this section focuses on a particular type of semiconductor, the transparent conducting oxides (TCOs). For semiconductors to be transparent they have to absorb light at energies higher than the highest energy of visible light, which correlates to ~ 3.0 eV. TCO materials must display high transparency ($> 80\%$ transmittance in the visible) and high electrical conductivity. Thin film TCOs play a major role in the fabrication of a range of devices including in solar cells, optical sensors, flat panel displays and architectural glass applications and they have been used in thin film transistor (TFT) applications. The conductivity of a semiconductor is at least an order of magnitude lower than that of a metal,¹²² however doping is a

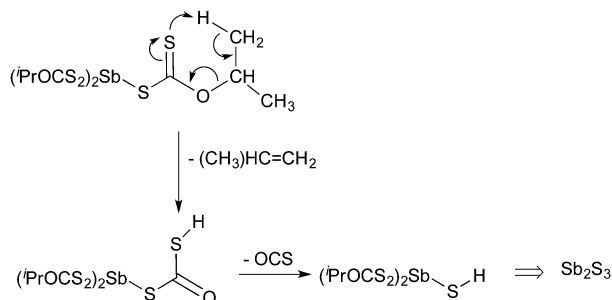

Scheme 4 Decomposition of $[\text{Sb}(\text{S}_2\text{COR})_3]$.



common method to increase conductivity whilst remaining optically transparent. Better drive capacities and electrical stability are key to the improvement of TFT technologies.^{123,124}

The vast majority of TCOs are based on In_2O_3 , SnO_2 , ZnO and their ternary metal oxides. These oxides exhibit n-type characteristics with electron mobility as high as $90 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$.¹²⁵ The development of p-type materials (hole transporting as opposed to the electron transporting, n-type) has been considerably slower. There have been many challenges faced in the development of materials exhibiting p-type characteristics^{126,127} and they are limited to materials, such as Cu_2O and SnO .¹²⁸

Recent research into the conductivity of n-type metal oxides has shown improvement in oxygen deficient films, leading to the belief that oxygen vacancies and metal interstitials act as electron donors.¹²⁹ Theoretical and experimental work has also shown that hydrogen could play a part in n-type conductivity.^{130,131} However, the more traditional route of introducing impurities, or doping, is still the favoured, more controlled method to enhancing the conducting properties of the material and recent developments in the AACVD of TCOs will be described (*vide infra*). As devices approach their top performance, cheaper alternatives are desired, driving forward the market of inexpensive disposable electronics. Solution deposition of semiconducting main group oxides has seen much growth in the last decade from both academic and industrial research labs.¹²⁹ Solution based techniques would simplify multi-step synthetic procedures and lower the cost whilst still delivering a high performance. Currently there are a number of solution based techniques all with their advantages and drawbacks, including sol-gel, spray pyrolysis and dip coating.^{132–134} A recent review describes the AACVD of organic–inorganic nanocomposite coatings using cold plasma¹³⁵ and ZnO materials and devices have also been reviewed.¹³⁶

Single-source or molecular precursors can be used for the formation of thin film metal oxide materials without an additional oxygen input.¹³⁷ These precursors can provide a clean and facile decomposition route that can often be more environmentally friendly, less toxic/expensive whilst at the same time eliminating the need for a mixture of precursors. Gallium oxide, indium oxide and tin oxide and their ternary oxides show excellent electrical conductivity and find application in the field of gas sensing (Section 6) and TCOs.¹³⁸

4.1 Gallium and indium oxides

The β -form or monoclinic phase of gallium oxide is the most common observed, which is not usually crystalline until 900°C , although there are reports of crystalline films grown at 600°C ,^{139,140} although this seems to be unusual with typical conversion occurring $\sim 700^\circ\text{C}$.¹⁴¹ Whilst gallium oxide is amorphous at lower temperatures it shows semiconducting behaviour above 450°C and changes in resistivity depending on the concentration of various reducing gases. Precursors to gallium oxide have received much interest and have been described in some reviews.^{137,142–144} Recent developments on the AACVD of gallium oxide are described below.

Single-source precursors of gallium oxide can be grouped into three major classes: alkoxides, β -diketonates and β -ketoimines

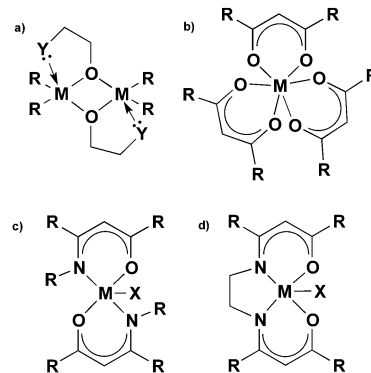


Fig. 17 Single-source precursors for gallium and indium oxide ($M = \text{Ga}, \text{In}$).

(Fig. 17). Gallium alkoxide precursors that yield thin films of Ga_2O_3 are well reported^{142,145} with synthetic routes including reaction of trialkyl gallium with alcohols,^{139,146} reaction of GaCl_3 with the salt of an alcohol¹⁴⁷ and reaction of gallium amides with alcohols.^{148,149} Within the remit of 'alkoxide' are a number of subdivisions, including the simpler monodentate alkoxides (*e.g.* methoxide, ethoxide) and also donor-functionalised alkoxides which are more commonly seen as precursors in AACVD because of their ability to split oligomers into monomers *via* the coordination of a Lewis base.¹⁴⁵ Whilst there are a number of variants to these donor-functionalised ligands, which improve solubility for use in AACVD and volatility for use in other types of CVD, carbon contamination is kept to a minimum with the use of shorter chains. As such it is more commonly seen that alcohols, of the type $\text{HOCH}_2\text{CH}_2\text{YR}_x$ ($\text{Y} = \text{O}$, $\text{R} = \text{Me}$, $x = 1$; $\text{Y} = \text{N}$, $\text{R} = \text{Me}$, Et , $x = 2$) are used in the vast majority of reported cases, with the YR_x moiety acting as the Lewis base.¹⁵⁰ The precursors were synthesized *via* a 1:1 reaction of GaMe_3 with a donor-functionalised alcohol to yield the gallium mono-alkoxides, $[\text{Me}_2\text{Ga}(\text{OCH}_2\text{CH}_2\text{YR}_x)]_2$.¹⁵¹ However, higher ratios of alcohol to trialkyl gallium resulted in the formation of mixtures of the gallium mono- and bis-alkoxides $[\text{Me}_{3-n}\text{Ga}(\text{OCH}_2\text{CH}_2\text{YR}_x)_n]$ ($n = 1, 2$).¹⁵² Monomeric gallium bis-alkoxides, of the type $[\text{ClGa}(\text{OCH}_2\text{CH}_2\text{YR}_x)_2]$ could be isolated from the reaction of GaCl_3 . In contrast, the addition of one equivalent of a donor-functionalised alcohol yields the dimeric gallium monoalkoxides, $[\text{Cl}_2\text{Ga}(\text{OCH}_2\text{CH}_2\text{YR}_x)]_2$ (Fig. 18).¹⁵³ A solution to this was the use of an amine elimination route, which enabled the isolation of mono-, bis- and tris-alkoxides, which have all been used to produce films of Ga_2O_3 *via* AACVD.^{153,154}

The alkylgallium mono-alkoxides were initially used in low pressure CVD, however oxygen deficient thin films of gallium oxide were deposited. AACVD was then investigated due to the high solubility of the precursors in a range of solvents and in order to deposit higher purity gallium oxide.^{139,140} Rather than isolate and purify the dialkylgallium monoalkoxide it was generated *in situ*. This resulted in the AACVD reaction of GaR_3 ($\text{R} = \text{Me}, \text{Et}$) and excess $\text{R}'\text{OH}$ ($\text{R}' = \text{C}(\text{CH}_3)_2\text{CH}_2\text{OMe}$, $\text{CH}_2\text{CH}_2\text{OMe}$, $\text{CH}_2\text{CH}_2\text{NMe}_2$, $\text{CH}(\text{CH}_3)\text{CH}_2\text{NMe}_2$, $\text{CH}(\text{CH}_2\text{NMe}_2)_2$) in toluene at 450°C yielding stoichiometric Ga_2O_3 thin films with minimal carbon contamination. The gallium oxide films showed minimal reflectivity (5–10%) and high transmission (80–90%) with



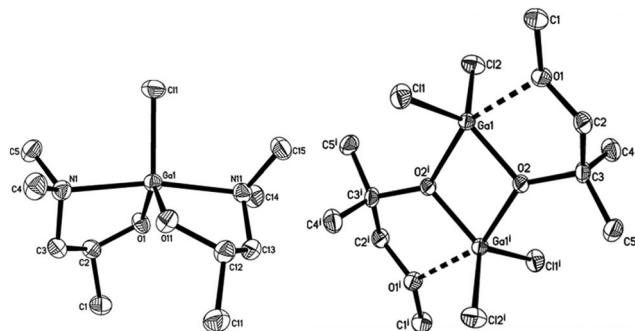


Fig. 18 Crystal structure of: left, $[\text{Ga}(\text{OCH}(\text{CH}_3)\text{CH}_2\text{NMe}_2)_2\text{Cl}]$, right, $[\text{Ga}(\text{OC}(\text{CH}_3)_2\text{CH}_2\text{OMe})\text{Cl}_2]_2$ both with thermal ellipsoids shown at the 50% probability level (hydrogen atoms omitted for clarity). Reproduced from ref. 153 with permission from the Centre National de la Recherche Scientifique (CNRS) and the Royal Society of Chemistry.

a band gap of 4.5 to 4.7 eV. Excess alcohol was used to reduce the oxygen deficiency of the films. The films deposited using GaEt_3 were transparent, whereas those from GaMe_3 were brown, which suggests a higher incorporation of carbon in the latter. The lower carbon observed when using the ethyl-derivative is most likely due to a facile β -hydride elimination being available for this ligand (but not the methyl).

Thin films of Ga_2O_3 have also been deposited by AACVD from the reaction of $[\text{Ga}(\text{NMe}_2)_3]_2$ with a range of donor-functionalised alcohols, ROH ($\text{R} = \text{CH}_2\text{CH}_2\text{NMe}_2$, $\text{CH}(\text{CH}_2\text{NMe}_2)_2$, $\text{CH}(\text{CH}_3)\text{CH}_2\text{NMe}_2$, $\text{CH}_2\text{CH}_2\text{OMe}$ and $\text{C}(\text{CH}_3)_2\text{CH}_2\text{OMe}$).¹⁴⁵ The films were deposited at 550 °C from toluene solutions and simply changing the donor-functionalised alcohol yielded differing morphologies. As shown in Fig. 19, a spherical morphology resulted from the use of $\text{HOCH}(\text{CH}_2\text{NMe}_2)_2$ with $[\text{Ga}(\text{NMe}_2)_3]_2$, whereas fractals resulted from $\text{HOCH}(\text{CH}_3)\text{CH}_2\text{NMe}_2$.

We have also used donor-functionalised groups to stabilize gallium hydride species, of the type $[\{\text{GaH}_2(\text{L}_1)\}_2]$ and $[\{\text{GaH}(\text{L}_2)\}_2]$

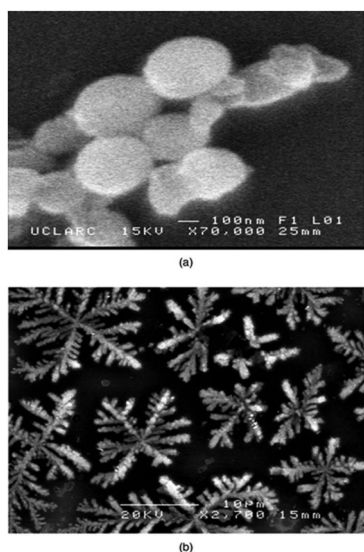


Fig. 19 SEM images of Ga_2O_3 deposited at 550 °C from $[\text{Ga}(\text{NMe}_2)_3]_2$ with (a) $\text{HOCH}(\text{CH}_2\text{NMe}_2)_2$ and (b) $\text{HOCH}(\text{CH}_3)\text{CH}_2\text{NMe}_2$ in toluene. Reproduced from ref. 154 with permission from The Royal Society of Chemistry.

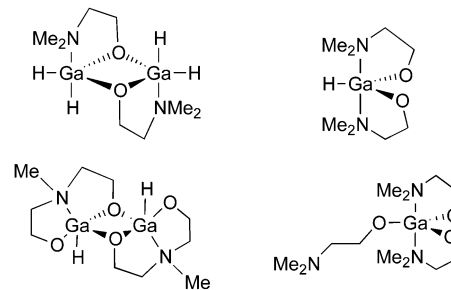


Fig. 20 Structural diagrams of $[\{\text{GaH}_2(\text{L}_1)\}_2]$ and $[\{\text{GaH}(\text{L}_2)\}_2]$ (where $\text{L} = \{\text{Me}_{3-x}\text{N}(\text{CH}_2\text{CH}_2\text{O})_x\}$ and $x = 1, 2$) and $[\text{Ga}(\text{L}_1)_3]$.

(where $\text{L}_x = \{\text{Me}_{3-x}\text{N}(\text{CH}_2\text{CH}_2\text{O})_x\}$ and $x = 1, 2$) that are stable and isolable at room temperature, as shown in Fig. 20.¹⁵⁵ The gallium tris(alkoxide) complex $[\text{Ga}(\text{L}_1)_3]$ and the related dimeric complex $[\{\text{GaMe}(\text{L}_2)\}_2]$, have also been used as single-source precursors for the deposition of Ga_2O_3 via AACVD with toluene as solvent. The resulting films were mostly transparent, indicating low levels of carbon contamination, and they were also mainly amorphous. The hydride compounds, $[\{\text{GaH}_2(\text{L}_1)\}_2]$ and $[\{\text{GaH}(\text{L}_2)\}_2]$, both afforded gallium-containing films, but the best film was deposited using homoleptic $[\text{Ga}(\text{L}_1)_3]$, which formed crystalline material, underneath microscale wires, at a substrate temperature of 450 °C.

As far back as 20 years ago commercially available 'simple' β -diketonates, such as $[\text{Ga}(\text{acac})_3]$, have been used to grow films of Ga_2O_3 with limited success and high carbon contamination was observed in the resulting films.^{156–158} Accessible through facile synthetic routes,^{159–161} gallium tris(β -diketonates) form air stable six coordinate octahedral species, of the type $[\text{Ga}(\text{O}_2\{\text{R}\})_3]$ ($\text{O}_2\{\text{R}\} = \beta$ -diketonate ligand). Recently, the use of these precursors for the deposition of spinel materials via AACVD has been reported.^{162,163} However, attempts to synthesise compounds of the type $[\text{GaX}(\text{O}_2\{\text{R}\})_2]$ ($\text{X} = \text{Cl}, \text{Me}, \text{H}$) for use in CVD failed and this further evidenced the thermodynamic stability of the homoleptic tris(β -diketonates) which formed instead.¹⁶⁴ Despite excellent solubility, the stability of gallium β -diketonates has meant that they are not ideal precursors for use in AACVD.

Gallium β -ketoiminate compounds are a more recent addition to the library of gallium precursors that currently exist. β -Ketoiminate ligands, when compared to bidentate ligands such as donor functionalised alcohols, have the advantage in that they can be easily tailored to be bi- or tetra dentate. The added functionality of groups attached to the nitrogen moiety in β -ketoimine ligands enables fine tuning of the precursor, in comparison to alkoxides and β -diketonates. The β -ketoiminate compounds contain a direct M–O bond within a delocalised ring including O and N donor atoms (Fig. 17), allowing more steric bulk to be brought into the coordination sphere of the metal centre, which can prevent oligomerisation improving precursor volatility and solubility. Furthermore, varying the R group on the N donor atom can not only increase the steric demand of the ligand, but also, with use of a polyether for example, yield multidentate ligands.¹⁴² AACVD of the β -ketoiminate gallium hydride compounds,



[GaH(L₃)] and [GaH₂(L₄)] (L₃ = (CH₂)₂{NC(Me)CHC(Me)=O}; L₄ = Me₂N(CH₂)₃NC(Me)CHC(Me)=O) in toluene at 450 °C deposited thin films of Ga₂O₃.¹⁶⁵ Superior films were deposited using [GaH(L₃)] (Fig. 17c and d, X = H) in comparison to [GaH₂(L₄)] resulting in transparent adherent films. These precursors also highlighted the advantages of AACVD as low pressure CVD was unsuccessful owing to the rapid decomposition of the precursors. However, solutions of the precursors were easily transported in an aerosol mist and deposited onto quartz substrates. Annealing the films at 1000 °C afforded crystalline films of Ga₂O₃. This work was particularly significant because it showed that compounds of this type could produce films with high transparency (80–90% in the visible) and low carbon contamination (<5%), significantly less than the brown films typically deposited *via* dialkylalkoxogallanes.^{139,151,154,166,167}

More recently, the effect of changing the β -ketoiminate ligand on the geometry and stability of gallium and aluminium precursors was studied.¹⁶⁸ The synthesis and crystal structures of $[\text{Ga}(\text{MeCN})\{\text{Pr}\}-\text{CHC}(\text{Me})=\text{O}\}_2\text{Cl}]$ in a trigonal bipyramidal geometry and $[\text{Ga}((\text{CH}_2)_2\{\text{NC}(\text{Me})-\text{CHC}(\text{C}_6\text{H}_5)=\text{O}\}_2)\text{Me}]$ in a square based pyramid were reported and their AACVD described (Fig. 21). Both compounds produced thin films of Ga_2O_3 on glass at $450\text{ }^\circ\text{C}$ with toluene as the solvent. In addition to gallium alkoxides and β -ketoiminates, gallium siloxide compounds, of the type $[\text{Me}_2\text{Ga}(\text{OR})_2]$ (SiEt_3 , $\text{Si}(\text{O}^t\text{Bu})_3$),¹⁶⁹ have been reported and their thermal degradation to Ga_2O_3 was proven *via* TGA.

Unlike the lighter members of group 13 the oxide of indium is cubic and crystalline at 300 °C, and no phase change is observed even under AACVD conditions of 600 °C. As a material, the oxide is used in a range of devices from solar cells to gas sensors, however routes to thin film deposition has posed a problem, largely due to the lack of suitable precursors. With a view to this there has been much work in the last decade on the synthesis of indium precursors that are soluble so that they can be used in the AACVD of In_2O_3 and a comprehensive review of indium precursors has been published.¹⁴²

In a similar manner to the gallium oxide precursors, indium oxide precursors can be grouped into two categories, namely alkoxides (Fig. 22) and β -diketonates until recently, however a range of β -ketoiminate precursors have now been reported.

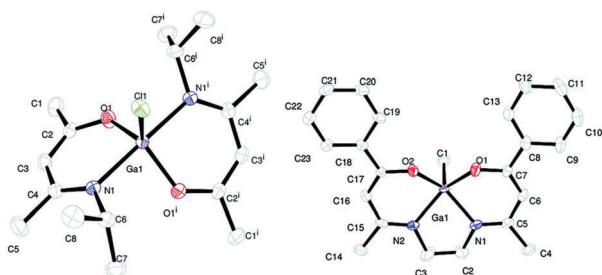


Fig. 21 ORTEP diagrams showing [Ga((Me)CN(H)^tPr)—CHC(Me)=O₂Cl], left and [Ga((CH₂)₂(N(H)C(Me)—CHC(C₆H₅)=O)₂Me], right. Thermal ellipsoids are drawn at 50% probability. Reproduced from ref. 168 with permission from the Centre National de la Recherche Scientifique (CNRS) and the Royal Society of Chemistry.

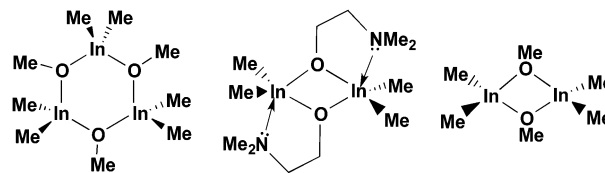


Fig. 22 Structures of dimethylindium alkoxides.

Literature routes to alkoxide compounds of indium often result in the formation of indium oxo alkoxo-clusters rather than isolated homoleptic alkoxides.¹⁷⁰ This may go some way towards explaining why the availability of volatile indium alkoxide precursors is limited. Bis- or tris-alkoxides of indium cannot be synthesised from reaction of InMe_3 and alcohols (mono- or donor-functionalised)¹⁷¹ and so amine elimination routes must be used, with $[\text{In}(\text{N}(\text{SiMe}_3)_2)_3]$ being a typical starting material.¹⁷² Whilst this can yield homoleptic complexes, attempts to synthesise heteroleptic indium alkoxides were unsuccessful and instead the silylamide group of the ligand was observed to migrate, resulting in the formation of dimeric species.¹⁷³

Solution based studies have shown that the reaction of InMe₃ and donor-functionalised alcohols form *in situ* compounds of the type [Me₂In(OR)]₂ (R = donor-functionalised ligand).^{171,174} As with gallium, this reaction of an alkyl indium species with a donor-functionalised alcohol (ROH, *e.g.* R = CH₂CH₂NMe₂, CH₂CH₂OMe) can be carried out *in situ* in the AACVD process, which removes the additional isolation step required in many techniques. These reactions in toluene solution can be made into an aerosol using an ultrasonic humidifier and used in AACVD to deposit thin films of In₂O₃ (Fig. 23). The films were deposited at 550 °C, of varying thickness indicated by the clearly visible interference fringes shown on the glass.¹⁷¹ The films were characterised fully and shown to displayed minimal reflectivity (5–10%) and high transmission (80–90%). Owing to the porosity of the films they were shown to be hydrophilic, with water contact angles of 28°. The success of this work highlighted not just the energy cost but also the time efficiency of *in situ* AACVD, and the methodology has since been applied to a number of systems. SEM of the films showed that a change in morphology was observed as the donor-functionalised alcohol was altered (Fig. 23).

Indium β -diketonate precursors, much like their gallium analogues are thermodynamically stable and sublimation of $[\text{In}(\text{acac})_3]$ is not observed until almost 200 °C.¹⁷⁵ As with the equivalent synthetic routes employed with gallium, attempts to isolate heteroleptic indium β -diketonates failed, with only the tris(β -diketonate) isolated.¹⁶⁴

It has been recently reported that the morphology of a film can be significantly altered by changing the solvent and/or temperature used in the AACVD process.¹⁷⁶ Thin films of In_2O_3 were deposited at 350–500 °C on glass from InMe_3 in methanol resulting in n-type conductivity with a resistivity of $8.60 \times 10^{-5} \Omega \text{ cm}$ and a charge carrier concentration of $9.30 \times 10^{20} \text{ cm}^{-3}$ with mobility of the charge carriers reported to be

$77.0 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$. For comparison, films of In_2O_3 were also deposited *via* AACVD from mixtures of InMe_3 and the donor functionalised alcohol, $\text{HOCH}_2\text{CH}_2\text{NMe}_2$ in methanol, which resulted in resistivity of $3.66 \times 10^{-5} \Omega \text{ cm}$ and a charge carrier concentration of $2.12 \times 10^{20} \text{ cm}^{-3}$ with mobility of the charge carriers reported to be $79.9 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$. Overall the presence of the donor-functionalised alcohol did improve the coverage and conductivity with the sheet resistance reported to be $4.88 \Omega \text{ sq}^{-1}$ compared with $3.44 \Omega \text{ sq}^{-1}$ for the InMe_3 /methanol system. SEM was used to compare the resultant morphologies of the films deposited. In_2O_3 deposited below 400°C from InMe_3 and methanol were flat and featureless, however increasing the deposition temperature to 450°C , resulted in the formation of agglomerated clusters, as shown in Fig. 24. The addition of the donor-functionalised alcohol gives a completely different morphology and the variation in film morphology was shown to be the result of changes in both temperature and the use of methanol.

Indium siloxide precursors of the type $[\text{Me}_2\text{In}(\text{OR})]$ ($\text{R} = \text{SiEt}_3$, $\text{OSi}(\text{O}^t\text{Bu})_3$),¹⁶⁹ have been synthesised and TGA analysis showed the former to thermally degrade to In_2O_3 , whilst the latter formed the silicate. More recent work from the same group has reported the synthesis of novel indium(III)-tin(II) alkoxides, which under thermal treatment yielded amorphous tin-rich ITO and crystalline ITO with traces of SnO_2 .¹⁷⁷

4.2 Ternary main group TCOs

Currently indium tin oxide (ITO) is the industrial standard and is used in most TCO materials. The availability of indium and therefore price still remains a concern and alternatives are actively being investigated. Gallium doped indium oxide, $\text{In}_2\text{O}_3:\text{Ga}$ and fluorine doped tin oxide, $\text{SnO}_2:\text{F}$ are two viable options and whilst these materials have been deposited by a range of techniques,^{178–180} the following section will give an overview of the recent developments in AACVD.

Gallium doped indium oxide $[\text{Ga}_x\text{In}_{1-x}\text{O}_3]$ has been shown to be an exceptional material for TCO applications with a transmittance that outstrips the competition.¹⁸¹ The material was successfully deposited for the first time *via* AACVD using a one pot reaction of GaMe_3 , InMe_3 and an excess of the donor-functionalised alcohol, $\text{HOCH}_2\text{CH}_2\text{OMe}$, in toluene at a range of temperatures, with 450°C found to be optimum.¹⁶⁶ The films

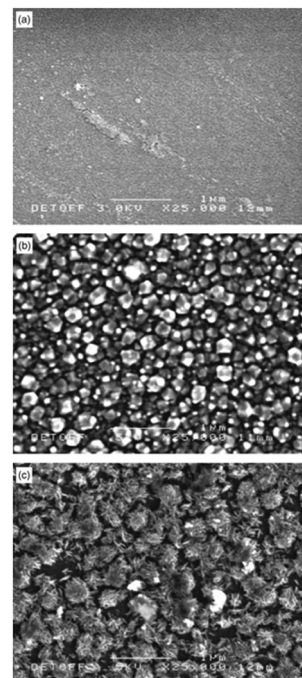


Fig. 24 SEM of films grown from AACVD deposition of InMe_3 and MeOH at (a) 400°C ; (b) 450°C ; and (c) 500°C . Reproduced with permission from ref. 176 Copyright 2013 Royal Australian Chemical Institute.

were transparent and XRD confirmed a homogeneously Ga substituted cubic In_2O_3 structure. There has been much interest in the synthesis of the best performing gallium doped indium oxide, not least for its improved transmission in the blue green.^{166,181} The material has been studied using a novel combinatorial AACVD (cAACVD) methodology (Fig. 25). The set up for cAACVD has two separate inlets, which when one is loaded with dopant and the other the main precursor gives rise to the production of films with a compositional gradient. A grid system is then used to analyse the films, such that conductivity, transmission, thickness, dopant% and film morphology, can all be mapped against each other. This method, despite requiring large amounts of analysis does provide a single deposition route to the optimisation of functional materials. This technique has been applied to LPCVD in the investigation of multi metallic oxide materials,^{182–184} APCVD for the synthesis of titanium oxide,¹⁶⁷ titanium oxynitride,¹⁸⁵ doping of photocatalytic films,¹⁸⁶ varying conductivity of vanadium oxide and oxynitride films,¹⁸⁷ doped titania films^{188,189} and varying niobium doping in anatase.¹⁹⁰

Combinatorial AACVD was used for the first time to produce films of gallium-indium-oxide which showed compositional gradient across the surface.¹⁹¹ Powder XRD, SEM, EDAX and UV/vis spectra were used to analyse films deposited at 400°C which showed Ga_2O_3 along the gallium precursor inlet, In_2O_3 along the indium precursor inlet and a compositional gradient between the two (Fig. 25). This initial study showed the potential of the technique, with increasing indium content correlating to increased conductivity and changes in the band gap, consistent with previously reported band gaps of indium and gallium oxide.¹⁸¹ Recently, cAACVD has been used to deposit

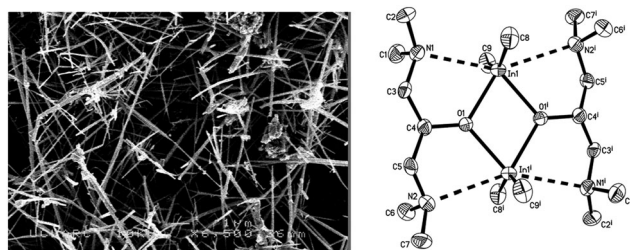


Fig. 23 Left, SEM image of In_2O_3 deposited from the reaction of InMe_3 and $\text{HOCH}_2\text{CH}_2\text{OMe}$ at 550°C , and right, X-ray structure of $[\text{Me}_2\text{In}(\text{OCH}(\text{CH}_2\text{NMe}_2)_2)]_2$ with thermal ellipsoids shown at the 50% probability level. Reproduced with permission from ref. 171. Copyright 2012 American Chemical Society.



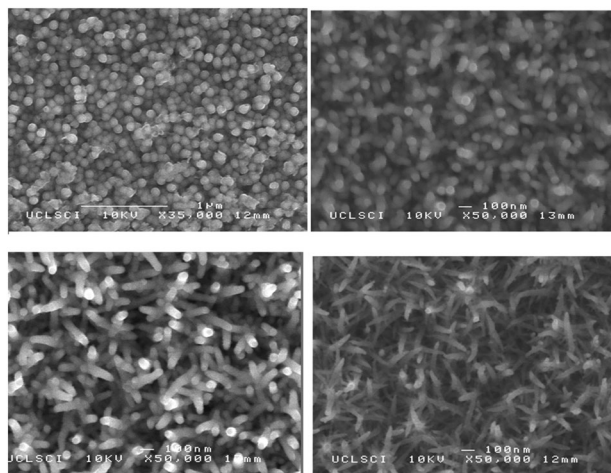


Fig. 25 Combinatorial AACVD: SEM images taken across the deposited film, showing the change from Ga_2O_3 (top left), through mixed gallium-indium-oxide (top right, bottom left) to In_2O_3 (bottom right). Reproduced from ref. 191 with permission from The Royal Society of Chemistry.

thin films of TiO_2 - SnO_2 composite materials for photocatalytic applications.¹⁹²

A very recent study described the use of AACVD to investigate the effect of doping indium oxide with molybdenum or tin.¹⁸⁴ Films were deposited at 450 °C, on glass substrates using methanol as a solvent from the precursors, $[\text{InCl}_3 \cdot x\text{H}_2\text{O}]$ and $[(\text{NH}_4)_6\text{Mo}_7\text{O}_{24} \cdot 4\text{H}_2\text{O}]$. The undoped In_2O_3 films gave high charge carrier concentrations ($1 \times 10^{20} \text{ cm}^{-3}$) and charge carrier mobilities ($71 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$). However, upon doping with Mo charge carrier concentration and charge carrier mobility both increased respectively ($4 \times 10^{20} \text{ cm}^{-3}$ and $119 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$) with no decrease in the transmittance. It was shown, using XPS, XAS and DFT calculations that Mo doping facilitated carrier mobility, in contrast to Sn doped In_2O_3 due to spatially separated conduction which in turn reduced the ionized impurity scattering that is observed in $\text{In}_2\text{O}_3:\text{Sn}$ (Fig. 26). It can be seen in Fig. 26 that the lower of the two curves, which represents regular ionized impurity scattering is significantly smaller than the higher mobility curve, which is due to scattering factors such as 'remote' impurities.¹⁹³

Thin films of ITO have also been deposited by AACVD using either aqueous or methanol solutions of $\text{InCl}_3 \cdot 4\text{H}_2\text{O}$ and 5 mol% $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$.¹⁹⁴ Crystalline films of ITO were grown with a (400) preferred orientation from aqueous solutions and a (440) preferred orientation from methanol, suggesting that the dissociation process of the droplets on the glass substrate and growing film surfaces is different for aqueous *versus* methanol solution droplets. Transparent conductive ITO films have also been deposited at 450–550 °C from a 0.2 M solution of $[\text{In}(\text{acac})_3]$ dissolved in acetylacetone with $[\text{Sn}(\text{acac})_2\text{Br}_2]$ added as a dopant.¹⁹⁵ The films showed excellent properties with ρ , n , and μ measured as $(1\text{--}2) \times 10^{-4} \Omega \text{ cm}$, $(1\text{--}3) \times 10^{21} \text{ cm}^{-3}$ and $(20\text{--}50) \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$, comparable to ITO films deposited *via* sputtering.

Nanocomposite films of ITO-Si have been successfully grown *via* AACVD. HRTEM showed that silicon nanocrystals were separated by 8.3 nm, with a density of $1.2 \times 10^{12} \text{ cm}^{-1}$.

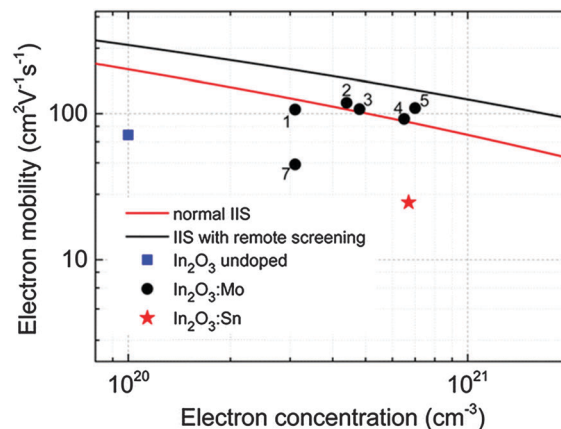


Fig. 26 Electron mobility and concentration for undoped, Sn-doped and Mo-doped In_2O_3 . The numbers by the data points correspond to the mol% of Mo dopant in the solution used in the AACVD. The model curves for regular ionized impurity scattering (IIS) (red line) and for remotely screened IIS (black line). All calculations are for singly ionized Mo donor atoms. Reproduced with permission from ref. 193. Copyright 2015 American Chemical Society.

Films were grown from a toluene solution of tin neodecanoate and ligand stabilised silicon nanocrystals onto glass substrates heated to 300 °C. Superior films gave sheet resistance of $400 \Omega \text{ square}^{-1}$. UV/vis provided evidence for the incorporation of the silicon nanocrystals into the ITO and it was determined that processing temperatures greater than 300 °C result in oxidation and lead to an increase in sheet resistance.¹⁹⁶

It is well known that doping tin oxide can improve the conductivity of the resultant TCO material, but it can also enhance other properties, such as optical transmittance or stability. ITO is the most commercially used TCO material but it is followed by fluorine doped tin oxide, $\text{SnO}_2:\text{F}$ (FTO) on which there is much information published in the literature.¹⁹⁷ There are a small range of precursors that have been used in the deposition of these materials, including tin alkoxides^{198,199} and β -diketonates,^{200,201} however only *via* techniques such as spin coating or spray pyrolysis,²⁰² traditionally tin halides and NH_4F or HF are used. In addition, antimony is a popular dopant, which like F alters the electronic properties of the TCO materials produced.^{203,204} Commercially available precursors, such as tin chloride and antimony chloride have been used^{205–207} to deposit thin films *via* a range of techniques including sol-gel,²⁰⁸ thermal evaporation²⁰⁹ and spray pyrolysis.^{205,210}

A recent study on the AACVD of FTO used a precursor, of the type $[\text{nBuSnCl}_{x-y}\text{F}_y]$, formed *in situ* by the halide exchange between *n*-butyltin trichloride and ammonium fluoride.²¹¹ Since isolation of the precursor was not possible, evidence for the formation included XRD identification of the NH_4Cl side product and XPS of the precursor, indicating the formation of a Sn-F bond. The AACVD method lends itself to *in situ* precursor synthesis, with the solution being immediately used to create an aerosol mist, thus removing the need for precursor isolation. This particular example highlighted the influence carrier solvent has on the functional properties of the materials.²¹² Varying the solvent had a significant effect on the film



The recent emergence of SnO, containing tin in its lower Sn(II) oxidation state, as a potential p-type material has generated much interest. A stannous ureid compound (Fig. 29) was synthesised by the addition of 2 equivalents of *tert*-butyl isocyanate to [Sn(NMe₂)₂]₂.²¹⁹ AACVD of the stannous ureid in toluene at 250–350 °C resulted in the deposition of tetragonal SnO films. Powder XRD showed that the only crystalline phase at temperatures > 300 °C was tetragonal SnO with no evidence of disproportionation to Sn(O) and SnO₂. Raman spectroscopy


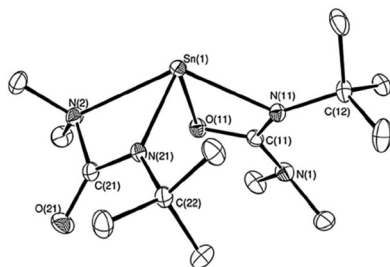


Fig. 29 Structure of the stannous ureid. Reproduced from ref. 218 with permission from The Royal Society of Chemistry.

confirmed the formation of SnO at all temperatures and no evidence of SnO₂ or other phases, such as Sn₂O₃ or Sn₃O₄ were observed. Some evidence of surface oxidation to Sn(IV) was observed but valence band XPS spectra showed that after argon etching of the films, Sn(II) was the prominent component with a leading valence band energy of ~2 eV. It is thought that the production of the metastable oxide, SnO, from the stannous ureid is the result of careful molecular design of the precursor and the kinetic outcome of a sequence of elimination reactions. Thin films of SnO were also deposited using the precursor [Sn(OSiMe₃)₂]₂ in an AACVD process with toluene as the solvent and deposition temperatures of 450 °C.²²⁰ Powder XRD confirmed the formation of SnO (and no Sn metal), which was surprising given the higher temperatures used in these depositions. SEM of the films showed the formation of irregular cubes of width about 100 nm on a thin film.

5 Main group photoelectrochemical and photocatalytic materials

Harvesting solar energy is a favourable alternative to burning fossil fuels however an issue that must be addressed is that of storing the electrical energy produced. This is why solar energy is preferably converted into chemical energy with the formation of hydrogen, which can be converted to electrical energy at a later stage. Water photolysis is a renewable, non-polluting method for H₂ fuel generation, however there are a number of technical challenges. Under acidic conditions solar energy is used to split water into oxygen at the anode (eqn (4)) and hydrogen at the cathode (eqn (5)). This is facilitated by the use of semiconductors that absorb at the correct wavelength that are dipped into an electrolytic solution.



Photocatalysts are sought to be used in this process, which must be suitable for large-scale application. Whilst many transition metal oxides are known, their band gaps (~3 eV) tend to be too large (for visible light irradiation) and as such many bismuth oxide systems, amongst some other materials have received recent attention in the literature, since the ideal band gap for a photoelectrochemical (PEC) material would be 2 eV.

PEC solar cells must have a band gap such that they can absorb the maximum amount of the visible region of the spectrum whilst remaining photostable. PEC materials have the ability to use solar energy to split water into oxygen and hydrogen, and their efficiency is dependent on band energetics, bulk structure and surface properties. Hydrogen has also been produced by photocatalytic and photoelectrochemical routes.^{221–223} In order to improve efficiencies and cut costs attempts have been made to increase surface area and shorten charge transport pathways.²²⁴ Whilst nanostructured photocatalysts have come some way to meeting these criteria the larger surface area encourages defect recombination, hinders electron hole separation and reduces the photovoltage. Recent development in the field has seen a turn to CVD in order to deposit films with tuned microstructure. AACVD lends itself to the fabrication of these devices, since surface morphology can be easily controlled in this solution based technique to improve PEC performance,²²⁵ unlike other forms of CVD or film deposition. We direct the attention of the reader to these useful articles on PEC cells for more in depth detail.^{226–229}

5.1 Bismuth oxide based materials

Bismuth oxide (Bi₂O₃) exists as a number of polymorphs and as such the band gap is reported to lie within the range 2.29–3.31 eV. The low temperature α phase is stable with the other phases being metastable. It was the discovery that metastable δ-Bi₂O₃ had the highest oxide ion conductivity of any material,²³⁰ that made it highly useful as an electrolyte, but it was its band gap that meant it was useful as a photocatalyst for degradation of pollutant dyes²³¹ and water splitting.²³² This versatile material has also found use in gas sensors,²³³ UV light photocatalyst,²³¹ ferroelectric,²³⁴ multiferroic²³⁵ and superconducting oxides.²³⁶ In comparison to some other main group elements, such as gallium, there are only a limited number of bismuth precursors available, despite the same obstacles to film deposition including precursor volatility, high deposition temperatures and carbon contamination, being faced. Key attributes to successful precursors are the inclusion of at least one Bi–O bond, to overcome the energy barrier of formation in the CVD reactor, another is the use of sterically demanding ligands such that oligomerisation does not occur, affording volatile, soluble precursors.²³⁷ In general, precursor compounds of bismuth can be grouped into 3 sections; alkoxides, β-diketonates and carboxylates. These precursors can be synthesised *via* a number of different routes, including alcoholysis of bismuth amides (e.g. [Bi(NMe₂)₃]₂)²³⁸ or the less air-sensitive bismuth silyl amide [Bi{N(SiMe₃)₂}]₃,²³⁹ or metathesis reaction of bismuth halides and alkoxide salts.²⁴⁰ Due to the poor volatility, solubility and sensitivity of bismuth alkoxides, donor functionalised bismuth compounds were synthesised and their use in LPCVD reported.^{241,242} To further understand the potential of bismuth alkoxides and β-diketonates as CVD precursors TGA was carried out on a range of compounds.²⁴² There are a number of reports of the deposition of thin films of Bi₂O₃ in the literature by a variety of techniques,¹⁴³ however this section will focus on recent developments in the AACVD of the material.



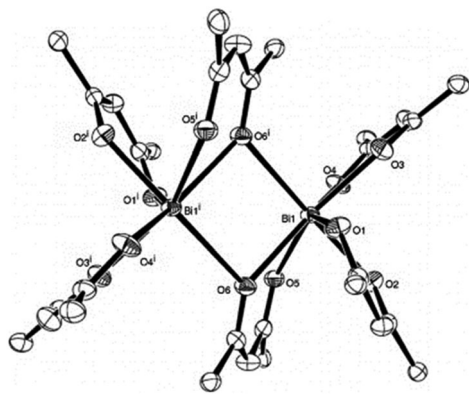


Fig. 30 X-ray crystallographic structure of $[\text{Bi}(\text{dbm})_3]_2$. Thermal ellipsoids set at 50% probability, phenyl rings, CH_2Cl_2 solvent and hydrogen atoms omitted for clarity. Reproduced with permission from ref. 243. Copyright 2012 Elsevier.

Bismuth β -diketonates have attracted attention as CVD precursors due to their increased stability to moisture; recently $[\text{Bi}(\text{dbm})_3]_2$ (dbm = dibenzoylmethane) was used as a precursor in AACVD of Bi_2O_3 at 460–525 °C (Fig. 30). The films were synthesised *via* a co-deposition in order to dope with platinum nanoparticles using $[\text{H}_2\text{PtCl}_6 \cdot \text{H}_2\text{O}]$ as the Pt precursor. Films were found to consist of $\text{Pt-Bi}_2\text{O}_3$, and the addition of Pt particles cause hydrogen evolution during photolysis of water, something that does not occur with Pt particles or Bi_2O_3 alone.²⁴³ More recently the isolation of a bismuth carbamate $[\text{Bi}(\text{O}_2\text{CN}^i\text{Pr}_2)_3]$ (Fig. 31), a tetramer in the solid-state, was used to deposit Bi_2O_3 *via* AACVD. It was shown in this study that $\delta\text{-Bi}_2\text{O}_3$ was initially deposited, which showed superior photocatalytic activity, and at longer deposition times a thick layer of $\beta\text{-Bi}_2\text{O}_3$ nanowires grew on top, which proved to be less active (Fig. 32). Films were deposited from a precursor solution in hexane, on glass at temperatures ranging from 300–450 °C from 10–40 minutes.²⁴⁴

5.2 Bismuth composite materials

As discussed above, there are a broad range of applications for bismuth oxide materials, as is true for its ternary and higher

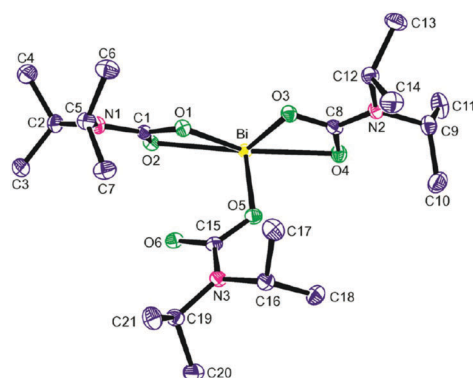


Fig. 31 Asymmetric unit of $[\text{Bi}(\text{O}_2\text{CN}^i\text{Pr}_2)_3]$ thermal ellipsoids are at 40% probability, the co-crystallised disordered solvent, and hydrogen atoms omitted for clarity. Reproduced with permission from ref. 244. Copyright 2013 American Chemical Society.

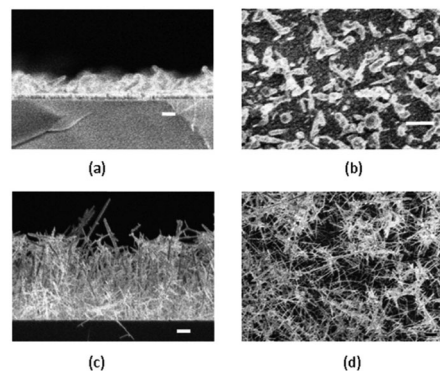


Fig. 32 SEM of the films grown from $[\text{Bi}(\text{O}_2\text{CN}^i\text{Pr}_2)_3]$, (a and b) at 300 °C for 40 minutes, and (c and d) at 450 °C for 40 minutes. Reproduced with permission from ref. 244. Copyright 2013 American Chemical Society.

oxide materials. There has been much work over the last decade in the area of precursor synthesis which includes bismuth and other metals within the same molecule, to be used as single-source precursors. We direct the reader's attention to a recent review in the area of bismuth precursor development for more detail²³⁷ and here focus on the upsurge in the last five years of AACVD in this area.

Bi_2S_3 has a band gap of 1.7 eV with an absorption coefficient of $104\text{--}105\text{ cm}^{-1}$, making it an attractive material for PEC applications.²⁴⁵ AACVD of bismuth selenide films was carried out using at 475 °C, with the precursor, $[\text{Bi}\{(\text{Se}^i\text{Pr}_2)_2\text{N}\}_3]$ dissolved in THF (*vide supra*).¹⁰⁸ The resulting crystalline Bi_2Se_3 films showed preferred orientation along the (006) direction. In the same report, $[\text{Bi}\{(\text{SPR}_2)_2\text{N}\}_3]$ ($\text{R} = ^i\text{Pr}$ or Ph) was used to deposit thin films of Bi_2S_3 at 425–475 °C, and despite poor morphology and crystallinity the band gap of the material was calculated to be 1.32 eV, in excellent agreement with the literature value of 1.3 eV. This study showed that AACVD was an excellent tool to control phase and morphology of the material (Fig. 33).¹¹⁶ AACVD was used again to deposit nanoparticles and tubes of Bi_2S_3 onto FTO coated glass. By varying the solvent used the surface morphology could be controlled; precursor solutions of $[\text{Bi}(\text{S}_2\text{CNET}_2)_3]_2$ in chloroform or dichloromethane yielded films of well defined nanotubes (diameter $\sim 40\text{ nm}$). Alternatively films deposited from chloroform/toluene mixtures gave compacted nanostructured morphology. Films were deposited at temperatures between 350–450 °C, and the band gap of the materials was calculated to be 1.85 and 1.8 eV respectively. PEC testing showed an excellent response, with photocurrent densities of 1.9 mA cm^{-2} and 1.0 mA cm^{-2} at 0.23 V *versus* $\text{Ag}|\text{AgCl}|3\text{ M}|\text{KCl}$, respectively.¹¹⁴

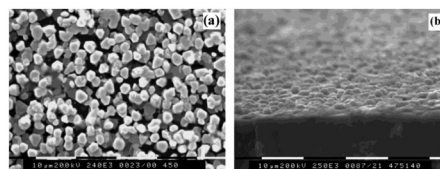


Fig. 33 SEM images of Bi_2Se_3 deposited from $[\text{Bi}(\text{N}(\text{Se}^i\text{Pr}_2)_2)_3]$ by AACVD at 475 °C on glass. Reproduced with permission from ref. 116. Copyright 2004 Copyright 2013 American Chemical Society.



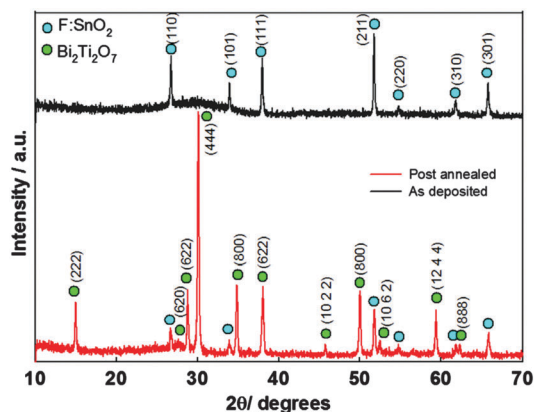


Fig. 34 X-ray diffraction pattern of the as-deposited (black) and post-annealed (red) $\text{Bi}_2\text{Ti}_2\text{O}_7$ thin film. Reproduced with permission from ref. 247. Copyright 2014 Elsevier.

Thin films of BiFeO₃ were synthesised *via* AACVD for the first time using the known heterometallic precursor [CpFe(CO)₂BiCl₂]²⁴⁶. Films were deposited on glass from a precursor solution in THF at 300 °C, resulting in dark orange adherent films. The band gap was calculated to lie between 2.0 and 2.2 eV and photocatalytic testing showed that the material was superior to TiO₂ industrial standards when irradiated under UVA (365 nm) with an average O₂ yield of 24.4% which represents a ten-fold increase over optimised B-doped TiO₂ films.

Bismuth titanate ($\text{Bi}_2\text{Ti}_2\text{O}_7$) thin films have been prepared for the first time *via* AACVD using bismuth nitrate pentahydrate in acetylacetone and titanium isopropoxide in methanol.²⁴⁷ The crystallinity of the films was improved by post annealing (Fig. 34). Films were deposited at 600 °C on FTO substrates, and then annealed at 600 °C for 12 hours in order to afford phase pure $\text{Bi}_2\text{Ti}_2\text{O}_7$ photoelectrodes. The photocurrent density was reported as $1.8 \mu\text{A cm}^{-1}$ at 0.23 V *versus* Ag|AgCl, with a direct bandgap of 2.74 eV, making it potentially better than TiO_2 , since it absorbs a greater proportion of the solar spectrum and exhibits less recombination.²⁴⁷ Thin films of phase pure bismuth vanadate (BiVO_4) photoelectrodes have also been prepared by AACVD on FTO glass substrates.²⁴⁸ Bismuth vanadate has a band gap of 2.4 eV in the monoclinic scheelite phase²⁴⁹ and is considered one of the most promising anodic semiconductor materials for PEC, not least because of its stability in pH neutral conditions.²⁵⁰ SEM images of the BiVO_4 films deposited *via* AACVD from bismuth nitrate pentahydrate in acetyl acetone and vanadyl acetyl acetone in methanol at 500 °C, showed that the film were porous (Fig. 35). This porosity results in the films having a larger effective surface area and an increased electrode/electrolyte interfacial area allowing for a reduction in electron-hole recombination. Powder XRD showed that the monoclinic scheelite crystal structure of BiVO_4 was adopted, which is ideal for PEC applications leading to superior PEC performance compared to other phases (Fig. 35). A Tauc plot showed the optical band gap to be 2.44 eV. The PEC properties were studied in aqueous 1 M Na_2SO_4 and showed a photocurrent density of 0.4 mA cm^{-2} and a maximum incident-photon-to-electron conversion efficiency (IPCE) of 19% at 1.23 V.

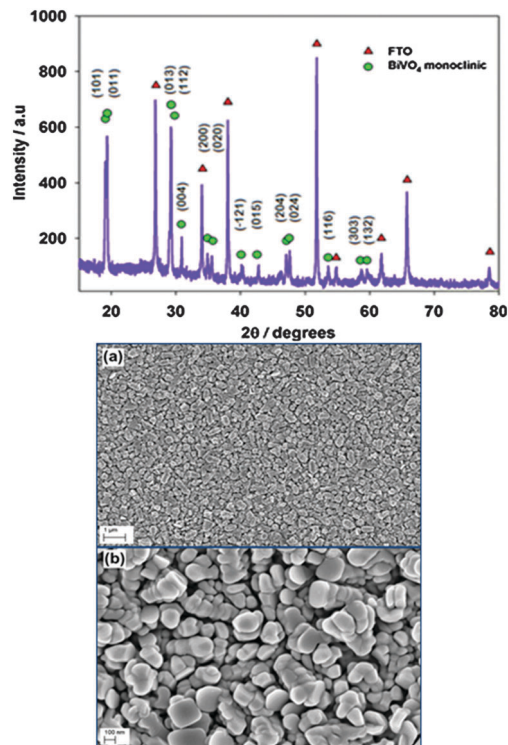


Fig. 35 XRD pattern of monoclinic BiVO₄ (green) on FTO (red) coated glass substrate deposited *via* AACVD; below: SEM image of BiVO₄ thin film at (a) 20 000 $\times$ and (b) 100 000 $\times$. Reproduced with permission from ref. 248. Copyright 2012 Wiley.

5.3 Other PEC materials

A selection of recently deposited PEC main group materials that utilise the AACVD technique in their fabrication are briefly summarised below.

Zinc sulfide films were deposited on FTO coated glass at temperatures between 375–475 °C from solutions of the novel precursors $[\text{Zn}(\text{S}_2\text{CNCy}_2)_2(\text{py})]$ (where Cy = cyclohexyl, py = pyridine) and $[\text{Zn}(\text{S}_2\text{CN}(\text{CH}_2\text{Ph})(\text{Me}))_2(\text{py})]$ in toluene (*vide supra*). The ZnS thin film electrode prepared showed promising properties for solar energy conversion and optoelectronic applications. Band gap energies of 3.36 and 3.40 eV were estimated respectively, with PEC studies showing that the films were photoactive under anodic bias conditions. It was shown that films deposited at lower temperatures (375 °C) consisted of cauliflower like structure, which was not present in films deposited at higher temperature (425 °C) (Fig. 36).³⁹

Thin films of indium sulfide were deposited *via* AACVD of novel compounds of the type, $[\text{In}(\text{S}_2\text{NRR}')_3 \cdot n(\text{py})]$.⁷⁷ Films of $\beta\text{-In}_2\text{S}_3$ were deposited on FTO coated glass substrates at 300, 350 and 400 °C, with SEM images showing that varying temperature of deposition or ligand (R, R' = ⁱPr, $n = 1.5$, $\text{NRR}' = \text{pip}$, $n = 0.5$, R = Bz, R' = Me, $n = 0$) had an affect on the morphology of the films deposited (*vide supra*). The band gap of the films deposited was calculated to be ~ 2.2 eV with the PEC properties yielding photocurrent densities of 1.25 and 0.65 mA cm⁻² at 0.23 V *versus* Ag|AgCl for the In_2S_3 films deposited at 400 °C and 350 °C respectively (Fig. 37). This was the highest photocurrent

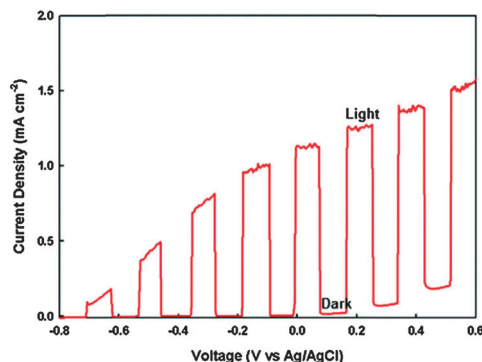


Fig. 36 J - V plot of In_2S_3 films obtained from AACVD at 400°C from $[\text{In}(\text{S}_2\text{CN}^i\text{Pr}_2)_3 \cdot 1.5(\text{py})]$. Reproduced with permission from ref. 85. Copyright 2013 Royal Society of Chemistry.

and the films were prepared using the precursor $[\text{In}(\text{S}_2\text{CN}^i\text{Pr}_2)_3 \cdot 1.5(\text{py})]$. The higher response compared to the films deposited from the other precursors was thought to be due to the uniform structure of the multi-shaped $\beta\text{-In}_2\text{S}_3$ crystallites in the film and better interconnections of particles in the film.

6 Main group gas sensing materials

Semiconducting metal oxides have been widely used in gas sensor devices since the absorption and desorption of a gas on the surface of a metal oxide changes the conductivity of the material.^{251,252} The sensitivity of the surface to a gas can be as low as parts per billion and ideally the metal oxide semiconductor sensor should have a large surface area in order to adsorb as much of the target analyte as possible on the surface to give a measurable response at such low concentrations. Gas sensor development have particularly focussed on the detection of species, such as CO_2 , CO , SO_2 , O_3 , NH_3 , NO_x and H_2 , due to atmospheric pollution, toxicity and that they can be found at high levels in some environments. Tin dioxide is used commercially as a gas sensor. However, the search for new gas sensing materials is of great interest as SnO_2 suffers from cross sensitivity issues, humidity interference and baseline drift. Main group materials that have been investigated for gas sensors applications include gallium oxide, indium oxide and tin dioxide.²⁵³ Fabrication methods need to be low cost, scalable and lead to films with appropriate morphology to achieve the required gas sensing response. Gas sensors have been widely reviewed^{251,252,254} including a recent review on the AACVD of some gas-sensitive nanomaterials.²⁵⁵ The following sections provide an up-to-date overview of main group oxide films grown by AACVD that have been investigated as gas sensors.

6.1 Gallium and indium oxide based materials

Gallium oxide (Ga_2O_3) is an ideal material for application as a thin film gas sensor as the function of the sensor can be switched with temperature. At temperatures below 900°C , gallium oxide thin film operates as a surface-control-type sensor to reducing gases, such as CO and ethanol. However, at temperatures above 900°C the

conductivity changes depend on the concentration of oxygen, therefore oxygen concentration can be monitored. Oxygen gas sensors have practical use in monitoring and controlling oxygen concentrations in waste gases, chemical processes and exhaust gases of automobiles. Thin films of Ga_2O_3 have been deposited from the *in situ* AACVD reaction of $[\text{Ga}(\text{NMe}_2)_3]_2$ and ROH ($\text{R} = \text{CH}_2\text{CH}_2\text{NMe}_2$, $\text{CH}(\text{CH}_2\text{NMe}_2)_2$, $\text{CH}(\text{CH}_3)\text{CH}_2\text{NMe}_2$, $\text{CH}_2\text{CH}_2\text{OMe}$ and $\text{C}(\text{CH}_3)_2\text{CH}_2\text{OMe}$) in toluene at 550°C (*vide supra*).¹⁵⁴ Transparent and unreflective films of gallium oxide were deposited from the reaction which generated gallium tris(alkoxides) *in situ*. The films were deposited on gas sensor substrates and an n-type response to ethanol at a range of temperatures was measured. Gas response was measured as the ratio between R (the resistance when exposed to ethanol) and R_0 (the point immediately preceding the introduction of ethanol). The gas response was rapid and the level did not vary much throughout the experimental process. The greatest response to a gas concentration of 100 ppm of ethanol was R/R_0 at 1.13. Screen-printed sensors showed a greater response ($R/R_0 = 2.12$), which is likely due to the thinner films produced by AACVD and differences in film morphology. However, CVD sensors have been shown to give a maximum response to oxidizing or reducing gases at significantly lower temperature ($100\text{--}250^\circ\text{C}$) than screen-printed sensors.¹⁵⁶

Indium oxide (In_2O_3) is used in industrial and technological applications, such as toxic/dangerous gas detection with particular sensitivity to reducing gases, such as ethanol and ammonia and oxidising gases such as O_3 . Thin films of In_2O_3 and $\text{In}_2\text{O}_3:\text{M}$ ($\text{M} = \text{Ti}$ or Ta) have been deposited on glass substrates *via* AACVD at 450°C from the *in situ* reaction of InMe_3 and $\text{HOCH}_2\text{CH}_2\text{NMe}_2$ and the addition of a transition metal alkoxide precursor (synthesised from the *in situ* reaction of $[\text{M}(\text{NMe}_2)_n]$ ($\text{M} = \text{Ti}$, $n = 4$; $\text{M} = \text{Ta}$, $n = 5$) and $\text{HOCH}_2\text{CH}_2\text{NMe}_2$) to produce the doped films, as shown in Scheme 5.²⁵⁶ The $\text{In}_2\text{O}_3:\text{M}$ films were found to contain 6.5 and 2.3 at% of Ti and Ta , respectively. Films deposited on gas sensing substrates were tested for their sensitivity to increasing concentrations of both reducing and oxidizing gases (ethanol, carbon monoxide, ammonia, NO_2). The tantalum doped indium oxide films ($\text{In}_2\text{O}_3:\text{Ta}$) showed an enhanced response, compared to In_2O_3 ,

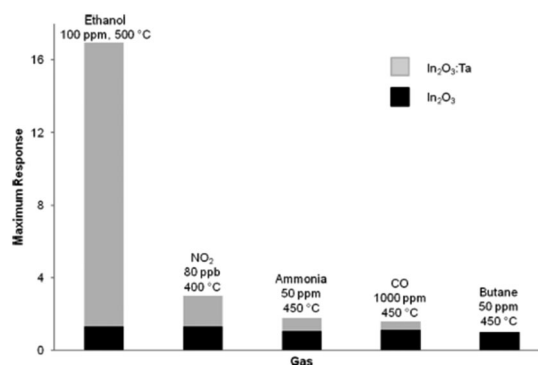


Fig. 37 Maximum gas response of In_2O_3 and $\text{In}_2\text{O}_3:\text{Ta}$ sensors to different gases in flowing air at optimum operating temperatures. Reproduced with permission from ref. 256. Copyright 2012 American Chemical Society.



Scheme 5 Deposition of In_2O_3 and $\text{In}_2\text{O}_3\text{:M}$ via AACVD.

Solution based techniques to TCO films are of key interest in order to simplify synthetic procedures and lower the cost whilst still delivering a high performance. AACVD has already been shown to be an excellent technique for the deposition of TCO films with figures of merit significantly beyond current commercial products. This is an area open for further research both within main group materials and other materials such as Nb-doped TiO_2 ,²⁶⁶ for the preparation of indium-free TCOs and the development of low-temperature routes. Furthermore, with careful design of the precursor in combination with the use of AACVD, p-type TCOs can be deposited which represents another area worthy of further research.

The EPSRC are thanked for grant EP/K001515.

- 1 *Chemical vapour deposition: precursors, processes and applications*, ed. A. C. Jones and M. L. Hitchman, Royal Society of Chemistry, Cambridge, UK, 2009.
- 2 P. Marchand, I. A. Hassan, I. P. Parkin and C. J. Carmalt, *Dalton Trans.*, 2013, **42**, 9406.
- 3 D. Bekermann, D. Barreca, A. Gasparotto and C. Maccato, *CrystEngComm*, 2012, **14**, 6347.
- 4 G. G. Condorelli, G. Malandrino and I. L. Fragalà, *Coord. Chem. Rev.*, 2007, **251**, 1931–1950.
- 5 A. Kurek, P. G. Gordon, S. Karle, A. Devi and S. T. Barry, *Aust. J. Chem.*, 2014, **67**, 989.
- 6 M. A. Malik, M. Afzaal and P. O'Brien, *Chem. Rev.*, 2010, **110**, 4417–4446.
- 7 O. Ambacher, *J. Phys. D: Appl. Phys.*, 1998, **31**, 2653–2710.
- 8 S. Strite, M. E. Lin and H. Morkoç, *Thin Solid Films*, 1993, **231**, 197–210.
- 9 *CVD of Compound Semiconductors*, ed. A. C. Jones and P. O'Brien, Wiley-VCH Verlag GmbH, Weinheim, Germany, 1997, pp. 319–320.
- 10 P. O'Brien and R. Nomura, *J. Mater. Chem.*, 1995, **5**, 1761.
- 11 H. M. Manasevit, *J. Cryst. Growth*, 1981, **55**, 1–9.

- Chem. Soc. Rev., 2016, 45, 1036–1064 | 1059

- 39 M. A. Ehsan, T. A. N. Peiris, K. G. U. Wijayantha, H. Khaledi, H. N. Ming, M. Misran, Z. Arifin and M. Mazhar, *Thin Solid Films*, 2013, **540**, 1–9.
- 40 S. Mlowe, D. J. Lewis, M. Azad Malik, J. Raftery, E. B. Mubofu, P. O'Brien and N. Revaprasadu, *New J. Chem.*, 2014, **38**, 6073–6080.
- 41 A. A. Memon, M. Dilshad, N. Revaprasadu, M. A. Malik, J. Raftery and J. Akhtar, *Turk. J. Chem.*, 2015, **39**, 169–178.
- 42 M. H. S. Wattoo, S. A. Tirmizi, A. Quddos, M. B. Khan, F. H. Wattoo, A. Wadood and A. B. Ghangro, *Arabian J. Sci. Eng.*, 2011, **36**, 565–571.
- 43 D. Oyetunde, M. Afzaal, M. A. Vincent, I. H. Hillier and P. O'Brien, *Inorg. Chem.*, 2011, **50**, 2052–2054.
- 44 S. S. Garje, J. S. Ritch, D. J. Eisler, M. Afzaal, P. O'Brien and T. Chivers, *J. Mater. Chem.*, 2006, **16**, 966–969.
- 45 M. C. Copsey, A. Panneerselvam, M. Afzaal, T. Chivers and P. O'Brien, *Dalton Trans.*, 2007, 1528.
- 46 I. D. Rojas-Montoya, A. Santana-Silva, V. García-Montalvo, M.-Á. Muñoz-Hernández and M. Rivera, *New J. Chem.*, 2014, **38**, 4702–4710.
- 47 H. M. Manasevit, *Appl. Phys. Lett.*, 1968, **12**, 156.
- 48 A. H. Cowley and R. A. Jones, *Polyhedron*, 1994, **13**, 1149–1157.
- 49 F. Maury, *Adv. Mater.*, 1991, **3**, 542–548.
- 50 R. L. Wells, S. R. Aubuchon, S. S. Kher, M. S. Lube and P. S. White, *Chem. Mater.*, 1995, **7**, 793–800.
- 51 S. Schulz, S. Fahrenholz, A. Kuczkowski, W. Assenmacher, A. Seemayer, A. Hommes and K. Wandelt, *Chem. Mater.*, 2005, **17**, 1982–1989.
- 52 C. J. Carmalt and S. Basharat, *Comprehensive Organometallic Chemistry III*, Elsevier, 2007, pp. 1–34.
- 53 I. M. Watson, *Coord. Chem. Rev.*, 2013, **257**, 2120–2141.
- 54 A. A. Wernberg, D. J. Lawrence, H. J. Gysling, A. J. Filo and T. N. Blanton, *J. Cryst. Growth*, 1993, **131**, 176–180.
- 55 M. Öztas, M. Bedir, R. Kayali and F. Aksoy, *J. Mater. Sci.: Mater. Electron.*, 2006, **17**, 841–845.
- 56 A. R. Raju, K. Sardar and C. N. R. Rao, *Mater. Sci. Semicond. Process.*, 2001, **4**, 549–553.
- 57 M. Puchinger, T. Wagner, D. Rodewald, J. Bill, F. Aldinger and F. F. Lange, *J. Cryst. Growth*, 2000, **208**, 153–159.
- 58 M. Puchinger, D. J. Kisailus, F. F. Lange and T. Wagner, *J. Cryst. Growth*, 2002, **245**, 219–227.
- 59 H. Luo, Y. Lin, H. Wang, J. H. Lee, N. A. Suvorova, A. H. Mueller, A. K. Burrell, T. M. McCleskey, E. Bauer, I. O. Usov, M. E. Hawley, T. G. Holesinger and Q. Jia, *Adv. Mater.*, 2009, **21**, 193–197.
- 60 J. F. Janik, M. Drygaś, S. Stelmakh, E. Grzanka, B. Pałosz and R. T. Paine, *Phys. Status Solidi A*, 2006, **203**, 1301–1306.
- 61 A. Iwata, J. Akedo and M. Lebedev, *J. Am. Ceram. Soc.*, 2005, **88**, 1067–1069.
- 62 S. Sathasivam, R. R. Arnepalli, B. Kumar, K. K. Singh, R. J. Visser, C. S. Blackman and C. J. Carmalt, *Chem. Mater.*, 2014, **26**, 4419–4424.
- 63 S. Sathasivam, R. R. Arnepalli, K. K. Singh, R. J. Visser, C. S. Blackman and C. J. Carmalt, *RSC Adv.*, 2015, **5**, 11812–11817.
- 64 D. A. Bohling, C. R. Abernathy and K. F. Jensen, *J. Cryst. Growth*, 1994, **136**, 118–126.
- 65 B. Q. Shi and C. W. Tu, *J. Electron. Mater.*, 1999, **28**, 43–49.
- 66 M. Bochmann, *Chem. Vap. Deposition*, 1996, **2**, 85–96.
- 67 M. Lazell, P. O'Brien, D. J. Otway and J.-H. Park, *J. Chem. Soc., Dalton Trans.*, 2000, 4479–4486.
- 68 N. Naghavi, E. Chassaing, M. Bouttemy, G. Rocha, G. Renou, E. Leite, A. Etcheberry and D. Lincot, *Energy Procedia*, 2011, **10**, 155–160.
- 69 *CVD of Nonmetals*, ed. W. S. Rees, Wiley-VCH Verlag GmbH, Weinheim, Germany, 1996.
- 70 F.-Y. Su, W.-D. Zhang, Y.-Y. Liu, R.-H. Huang and Y.-X. Yu, *J. Solid State Electrochem.*, 2015, **19**, 2321–2330.
- 71 S. Gledhill, R. Allison, N. Allsop, Y. Fu, E. Kanaki, R. Sáez-Araoz, M. Lux-Steiner and C.-H. Fischer, *Thin Solid Films*, 2011, **519**, 6413–6419.
- 72 M. Wang, X. Hou, J. Liu, K. Choy, P. Gibson, E. Salem, D. Koutsogeorgis and W. Cranton, *Phys. Status Solidi A*, 2015, **212**, 72–75.
- 73 K. George, C. H. (Kees) de Groot, C. Gurnani, A. L. Hector, R. Huang, M. Jura, W. Levason and G. Reid, *Chem. Mater.*, 2013, **25**, 1829–1836.
- 74 S. Suh and D. M. Hoffman, *Chem. Mater.*, 2000, **12**, 2794–2797.
- 75 J. J. Vittal and M. T. Ng, *Acc. Chem. Res.*, 2006, **39**, 869–877.
- 76 S. W. Haggata, M. A. Malik, M. Motevalli, P. O'Brien and J. C. Knowles, *Chem. Mater.*, 1995, **7**, 716–724.
- 77 A. Keys, S. G. Bott and A. R. Barron, *Chem. Mater.*, 1999, **11**, 3578–3587.
- 78 G. Shang, M. J. Hampden-Smith and E. N. Duesler, *Chem. Commun.*, 1996, 1733.
- 79 T. C. Deivaraj, J.-H. Park, M. Afzaal and J. J. Vittal, *Chem. Mater.*, 2003, **15**, 2383–2391.
- 80 J.-H. Park, M. Afzaal, M. Helliwell, M. A. Malik, P. O'Brien and J. Raftery, *Chem. Mater.*, 2003, **15**, 4205–4210.
- 81 M. Afzaal, D. Crouch, P. O'Brien and J.-H. Park, *J. Mater. Sci.: Mater. Electron.*, 2003, **14**, 555–557.
- 82 S. N. Malik, A. Q. Malik, R. F. Mehmood, G. Murtaza, Y. G. Alghamdi and M. A. Malik, *New J. Chem.*, 2015, **39**, 4047–4054.
- 83 S. Mahboob, S. N. Malik, N. Haider, C. Q. Nguyen, M. A. Malik and P. O'Brien, *J. Cryst. Growth*, 2014, **394**, 39–48.
- 84 S. S. Garje, M. C. Copsey, M. Afzaal, P. O'Brien and T. Chivers, *J. Mater. Chem.*, 2006, **16**, 4542.
- 85 M. A. Ehsan, T. A. N. Peiris, K. G. U. Wijayantha, M. M. Olmstead, Z. Arifin, M. Mazhar, K. M. Lo and V. McKee, *Dalton Trans.*, 2013, **42**, 10919.
- 86 J.-H. Park, M. Afzaal, M. Kemmler, P. O'Brien, D. J. Otway, J. Raftery and J. Waters, *J. Mater. Chem.*, 2003, **13**, 1942.
- 87 J. A. Andrade-Arvizu, M. Courel-Piedrahita and O. Vigil-Galán, *J. Mater. Sci.: Mater. Electron.*, 2015, **26**, 4541–4556.
- 88 B. Thangaraju and P. Kaliannan, *J. Phys. D: Appl. Phys.*, 2000, **33**, 1054–1059.
- 89 C. Gao and H. Shen, *Thin Solid Films*, 2012, **520**, 3523–3527.
- 90 P. Sinsermsuksakul, J. Heo, W. Noh, A. S. Hock and R. G. Gordon, *Adv. Energy Mater.*, 2011, **1**, 1116–1125.



- 91 S. C. Ray, M. K. Karanjai and D. DasGupta, *Thin Solid Films*, 1999, **350**, 72–78.
- 92 D. J. Lewis, P. Kevin, O. Bakr, C. A. Muryn, M. A. Malik and P. O'Brien, *Inorg. Chem. Front.*, 2014, **1**, 577.
- 93 I. P. Parkin, L. S. Price, T. G. Hibbert and K. C. Molloy, *J. Mater. Chem.*, 2001, **11**, 1486–1490.
- 94 G. Barone, T. G. Hibbert, M. F. Mahon, K. C. Molloy, L. S. Price, I. P. Parkin, A. M. E. Hardy and M. N. Field, *J. Mater. Chem.*, 2001, **11**, 464–468.
- 95 Y. S. Niwate, S. S. Garje, P. K. Giri, D. K. Goswami, A. Perumal and A. Chattopadhyay, *AIP Conf. Proc.*, 2010, **1276**, 56–61.
- 96 B. P. Bade, S. S. Garje, Y. S. Niwate, M. Afzaal and P. O'Brien, *Chem. Vap. Deposition*, 2008, **14**, 292–295.
- 97 K. Ramasamy, V. L. Kuznetsov, K. Gopal, M. A. Malik, J. Raftery, P. P. Edwards and P. O'Brien, *Chem. Mater.*, 2013, **25**, 266–276.
- 98 P. Kevin, D. J. Lewis, J. Raftery, M. Azad Malik and P. O'Brien, *J. Cryst. Growth*, 2015, **415**, 93–99.
- 99 P. Kevin, M. A. Malik and P. O'Brien, *J. Mater. Chem. C*, 2015, **3**, 5733–5741.
- 100 P. Kevin, S. N. Malik, M. A. Malik and P. O'Brien, *Chem. Commun.*, 2014, **50**, 14328–14330.
- 101 R. K. Sharma, G. Kedarnath, A. Wadawale, C. A. Betty, B. Vishwanadh and V. K. Jain, *Dalton Trans.*, 2012, **41**, 12129.
- 102 J. Akhtar, M. A. Malik, P. O'Brien and M. Helliwell, *J. Mater. Chem.*, 2010, **20**, 6116.
- 103 M. Afzaal, K. Ellwood, N. L. Pickett, P. O'Brien, J. Raftery and J. Waters, *J. Mater. Chem.*, 2004, **14**, 1310.
- 104 J. M. Clark, G. Kociok-Köhn, N. J. Harnett, M. S. Hill, R. Hill, K. C. Molloy, H. Saponia, D. Stanton and A. Sudlow, *Dalton Trans.*, 2011, **40**, 6893.
- 105 J. Akhtar, M. Afzaal, M. A. Vincent, N. A. Burton, I. H. Hillier and P. O'Brien, *Chem. Commun.*, 2011, **47**, 1991.
- 106 J. Akhtar, M. A. Malik, S. K. Stubbs, P. O'Brien, M. Helliwell and D. J. Binks, *Eur. J. Inorg. Chem.*, 2011, 2984–2990.
- 107 J. S. Ritch, T. Chivers, K. Ahmad, M. Afzaal and P. O'Brien, *Inorg. Chem.*, 2010, **49**, 1198–1205.
- 108 M. Madoun, R. Baghdad, K. Chebbah, M. A. Bezzerrouk, L. Michez and N. Benramdane, *Mater. Sci. Semicond. Process.*, 2013, **16**, 2084–2090.
- 109 A. J. MacLachlan, F. T. F. O'Mahony, A. L. Sudlow, M. S. Hill, K. C. Molloy, J. Nelson and S. A. Haque, *Chem-PhysChem*, 2014, **15**, 1019–1023.
- 110 C. Gao, H. Shen, L. Sun and Z. Shen, *Appl. Surf. Sci.*, 2011, **257**, 7529–7533.
- 111 P. Hu, Y. Cao and B. Lu, *Mater. Lett.*, 2013, **106**, 297–300.
- 112 J. B. Biswal, S. S. Garje, J. Nuwad and C. G. S. Pillai, *J. Solid State Chem.*, 2013, **204**, 348–355.
- 113 T. J. Groshens, R. W. J. Gedridge and C. K. Lowe-Ma, *Chem. Mater.*, 1994, **6**, 727–729.
- 114 A. A. Tahir, M. A. Ehsan, M. Mazhar, K. G. U. Wijayantha, M. Zeller and A. D. Hunter, *Chem. Mater.*, 2010, **22**, 5084–5092.
- 115 O. C. Monteiro, T. Trindade, F. A. A. Paz, J. Klinowski, J. Waters and P. O'Brien, *J. Mater. Chem.*, 2003, **13**, 3006.
- 116 J. Waters, D. Crouch, J. Raftery and P. O'Brien, *Chem. Mater.*, 2004, **16**, 3289–3298.
- 117 S. S. Garje, D. J. Eisler, J. S. Ritch, M. Afzaal, P. O'Brien and T. Chivers, *J. Am. Chem. Soc.*, 2006, **128**, 3120–3121.
- 118 J. R. Castro, K. C. Molloy, Y. Liu, C. S. Lai, Z. Dong, T. J. White and E. R. T. Tiekink, *J. Mater. Chem.*, 2008, **18**, 5399.
- 119 J. Rodriguez-Castro, M. F. Mahon and K. C. Molloy, *Chem. Vap. Deposition*, 2006, **12**, 601–607.
- 120 J. B. Biswal, N. V. Sawant and S. S. Garje, *Thin Solid Films*, 2010, **518**, 3164–3168.
- 121 R. K. Sharma, G. Kedarnath, V. K. Jain, A. Wadawale, M. Nalliath, C. G. S. Pillai and B. Vishwanadh, *Dalton Trans.*, 2010, **39**, 8779.
- 122 P. P. Edwards, A. Porch, M. O. Jones, D. V. Morgan and R. M. Perks, *Dalton Trans.*, 2004, 2995.
- 123 J. Y. Kwon, K. S. Son, J. S. Jung, T. S. Kim, M. K. Ryu, K. B. Park, B. W. Yoo, J. W. Kim, Y. G. Lee, K. C. Park, S. Y. Lee and J. M. Kim, *IEEE Electron Device Lett.*, 2008, **29**, 1309–1311.
- 124 R. A. Street, *Adv. Mater.*, 2009, **21**, 2007–2022.
- 125 M.-G. Kim, H. S. Kim, Y.-G. Ha, J. He, M. G. Kanatzidis, A. Facchetti and T. J. Marks, *J. Am. Chem. Soc.*, 2010, **132**, 10352–10364.
- 126 M. D. McCluskey and S. J. Jokela, *J. Appl. Phys.*, 2009, **106**, 071101.
- 127 D. O. Scanlon and G. W. Watson, *J. Mater. Chem.*, 2012, **22**, 25236.
- 128 A. Togo, F. Oba, I. Tanaka and K. Tatsumi, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2006, **74**, 195128, DOI: 10.1103/PhysRevB.74.195128.
- 129 S. R. Thomas, P. Pattanasattayavong and T. D. Anthopoulos, *Chem. Soc. Rev.*, 2013, **42**, 6910.
- 130 A. Janotti and C. G. Van de Walle, *Nat. Mater.*, 2007, **6**, 44–47.
- 131 Y. J. Li, T. C. Kaspar, T. C. Droubay, A. G. Joly, P. Nachimuthu, Z. Zhu, V. Shutthanandan and S. A. Chambers, *J. Appl. Phys.*, 2008, **104**, 053711.
- 132 S. Hwang, J. H. Lee, C. H. Woo, J. Y. Lee and H. K. Cho, *Thin Solid Films*, 2011, **519**, 5146–5149.
- 133 G. Adamopoulos, A. Bashir, P. H. Wöbkenberg, D. D. C. Bradley and T. D. Anthopoulos, *Appl. Phys. Lett.*, 2009, **95**, 133507.
- 134 B. N. Pal, B. M. Dhar, K. C. See and H. E. Katz, *Nat. Mater.*, 2009, **8**, 898–903.
- 135 F. Fanelli and F. Fracassi, *Plasma Chem. Plasma Process.*, 2014, **34**, 473–487.
- 136 Ü. Özgür, Y. I. Alivov, C. Liu, A. Teke, M. A. Reshchikov, S. Doğan, V. Avrutin, S.-J. Cho and H. Morkoç, *J. Appl. Phys.*, 2005, **98**, 041301.
- 137 P. Marchand and C. J. Carmalt, *Coord. Chem. Rev.*, 2013, **257**, 3202–3221.
- 138 C. G. Granqvist, *Sol. Energy Mater. Sol. Cells*, 2007, **91**, 1529–1598.
- 139 S. Basharat, W. Betchley, C. J. Carmalt, S. Barnett, D. A. Tocher and H. O. Davies, *Organometallics*, 2007, **26**, 403–407.



- 140 Y. Kokubun, K. Miura, F. Endo and S. Nakagomi, *Appl. Phys. Lett.*, 2007, **90**, 031912.
- 141 S. Mishra, S. Daniele, S. Petit, E. Jeanneau and M. Rolland, *Dalton Trans.*, 2009, 2569.
- 142 L. G. Bloor, C. J. Carmalt and D. Pugh, *Coord. Chem. Rev.*, 2011, **255**, 1293–1318.
- 143 D. Pugh, L. Bloor, S. Moniz and C. J. Carmalt, *Comprehensive Inorganic Chemistry II*, Elsevier, 2013, pp. 1021–1052.
- 144 M. Hellwig, K. Xu, D. Barreca, A. Gasparotto, M. Winter, E. Tondello, R. A. Fischer and A. Devi, *Eur. J. Inorg. Chem.*, 2009, 1110–1117.
- 145 C. Carmalt and S. King, *Coord. Chem. Rev.*, 2006, **250**, 682–709.
- 146 C. E. Knapp, D. A. Wann, A. Bil, J. T. Schirlin, H. E. Robertson, P. F. McMillan, D. W. H. Rankin and C. J. Carmalt, *Inorg. Chem.*, 2012, **51**, 3324–3331.
- 147 Y. Chi, T.-Y. Chou, Y.-J. Wang, S.-F. Huang, A. J. Carty, L. Scoles, K. A. Udachin, S.-M. Peng and G.-H. Lee, *Organometallics*, 2004, **23**, 95–103.
- 148 M. Valet and D. M. Hoffman, *Chem. Mater.*, 2001, **13**, 2135–2143.
- 149 L. Miinea, S. Suh, S. G. Bott, J.-R. Liu, W.-K. Chu and D. M. Hoffman, *J. Mater. Chem.*, 1999, **9**, 929–935.
- 150 C. E. Knapp, D. Pugh, P. F. McMillan, I. P. Parkin and C. J. Carmalt, *Inorg. Chem.*, 2011, **50**, 9491–9498.
- 151 C. E. Knapp, L. Pemberton, C. J. Carmalt, D. Pugh, P. F. McMillan, S. A. Barnett and D. A. Tocher, *Main Group Chem.*, 2010, 31–40.
- 152 S. Basharat, C. J. Carmalt, S. J. King, E. S. Peters and D. A. Tocher, *Dalton Trans.*, 2004, 3475.
- 153 S. Basharat, C. E. Knapp, C. J. Carmalt, S. A. Barnett and D. A. Tocher, *New J. Chem.*, 2008, **32**, 1513.
- 154 S. Basharat, C. J. Carmalt, R. Binions, R. Palgrave and I. P. Parkin, *Dalton Trans.*, 2008, 591.
- 155 D. Pugh, L. G. Bloor, I. P. Parkin and C. J. Carmalt, *Chem. – Eur. J.*, 2012, **18**, 6079–6087.
- 156 R. Binions, C. J. Carmalt, I. P. Parkin, K. F. E. Pratt and G. A. Shaw, *Chem. Mater.*, 2004, **16**, 2489–2493.
- 157 T. Maruyama and S. Arai, *Appl. Phys. Lett.*, 1992, **60**, 322.
- 158 J. S. Kim, H. A. Marzouk, P. J. Reucroft, J. D. Robertson and C. E. Hamrin, *Thin Solid Films*, 1993, **230**, 156–159.
- 159 Q. Peng, D. Hojo, K. J. Park and G. N. Parsons, *Thin Solid Films*, 2008, **516**, 4997–5003.
- 160 B. Ballarin, G. A. Battiston, F. Benetollo, R. Gerbasi, M. Porchia, D. Favretto and P. Traldi, *Inorg. Chim. Acta*, 1994, **217**, 71–78.
- 161 A. Ortiz, J. C. Alonso, E. Andrade and C. Urbiola, *J. Electrochem. Soc.*, 2001, **148**, F26.
- 162 C. E. Knapp, I. D. Prassides, S. Sathasivam, I. P. Parkin and C. J. Carmalt, *ChemPlusChem*, 2014, **79**, 122–127.
- 163 C. E. Knapp, J. A. Manzi, A. Kafizas, I. P. Parkin and C. J. Carmalt, *ChemPlusChem*, 2014, **79**, 1024–1029.
- 164 D. Pugh, L. G. Bloor, S. Sathasivam, I. P. Parkin and C. J. Carmalt, *Eur. J. Inorg. Chem.*, 2011, 1953–1960.
- 165 D. Pugh, P. Marchand, I. P. Parkin and C. J. Carmalt, *Inorg. Chem.*, 2012, **51**, 6385–6395.
- 166 C. E. Knapp, G. Hyett, I. P. Parkin and C. J. Carmalt, *Chem. Mater.*, 2011, **23**, 1719–1726.
- 167 G. Hyett, M. Green and I. P. Parkin, *J. Am. Chem. Soc.*, 2006, **128**, 12147–12155.
- 168 C. E. Knapp, P. Marchand, C. Dyer, I. P. Parkin and C. J. Carmalt, *New J. Chem.*, 2015, **39**, 6585–6592.
- 169 K. Samedov, Y. Aksu and M. Driess, *ChemPlusChem*, 2012, **77**, 663–674.
- 170 D. C. Bradley, H. Chudzynska, D. M. Frigo, M. B. Hursthouse and M. A. Mazid, *J. Chem. Soc., Chem. Commun.*, 1988, 1258.
- 171 S. Basharat, C. J. Carmalt, S. A. Barnett, D. A. Tocher and H. O. Davies, *Inorg. Chem.*, 2007, **46**, 9473–9480.
- 172 S. Suh and D. M. Hoffman, *J. Am. Chem. Soc.*, 2000, **122**, 9396–9404.
- 173 M. Veith, S. Hill and V. Huch, *Eur. J. Inorg. Chem.*, 1999, 1343–1350.
- 174 S. Basharat, C. J. Carmalt, R. Palgrave, S. A. Barnett, D. A. Tocher and H. O. Davies, *J. Organomet. Chem.*, 2008, **693**, 1787–1796.
- 175 T. Maruyama and K. Fukui, *J. Appl. Phys.*, 1991, **70**, 3848.
- 176 I. A. Hassan, A. Ratnasothy, D. S. Bhachu, S. Sathasivam and C. J. Carmalt, *Aust. J. Chem.*, 2013, **66**, 1274–1280.
- 177 P. W. Menezes, A. Indra, P. Littlewood, M. Schwarze, C. Göbel, R. Schomäcker and M. Driess, *ChemSusChem*, 2014, **7**, 2202–2211.
- 178 L. Körösi, S. Papp and I. Dékány, *Thin Solid Films*, 2011, **519**, 3113–3118.
- 179 J. Liu, A. W. Hains, L. Wang and T. J. Marks, *Thin Solid Films*, 2010, **518**, 3694–3699.
- 180 M. A. Aouaj, R. Diaz, A. Belayachi, F. Rueda and M. Abd-Lefdil, *Mater. Res. Bull.*, 2009, **44**, 1458–1461.
- 181 A. Wang, N. L. Edleman, J. R. Babcock, T. J. Marks, M. A. Lane, P. R. Brazis and C. R. Kannewurf, *J. Mater. Res.*, 2002, **17**, 3155–3162.
- 182 R. C. Smith, N. Hoilien, J. Roberts, S. A. Campbell and W. L. Gladfelter, *Chem. Mater.*, 2002, **14**, 474–476.
- 183 L. Zhong, Z. Zhang, S. A. Campbell and W. L. Gladfelter, *J. Mater. Chem.*, 2004, **14**, 3203.
- 184 B. Xia, F. Chen, S. A. Campbell, J. T. Roberts and W. L. Gladfelter, *Chem. Vap. Deposition*, 2004, **10**, 195–200.
- 185 G. Hyett, M. A. Green and I. P. Parkin, *J. Am. Chem. Soc.*, 2007, **129**, 15541–15548.
- 186 A. Kafizas, D. Adriaens, A. Mills and I. P. Parkin, *Phys. Chem. Chem. Phys.*, 2009, **11**, 8367.
- 187 A. Kafizas, G. Hyett and I. P. Parkin, *J. Mater. Chem.*, 2009, **19**, 1399.
- 188 A. Kafizas and I. P. Parkin, *J. Mater. Chem.*, 2010, **20**, 2157.
- 189 S. Sathasivam, A. Kafizas, S. Ponja, N. Chadwick, D. S. Bhachu, S. M. Bawaked, A. Y. Obaid, S. Al-Thabaiti, S. N. Basahel, C. J. Carmalt and I. P. Parkin, *Chem. Vap. Deposition*, 2014, **20**, 69–79.
- 190 A. Kafizas, C. W. Dunnill and I. P. Parkin, *J. Mater. Chem.*, 2010, **20**, 8336.
- 191 C. E. Knapp, A. Kafizas, I. P. Parkin and C. J. Carmalt, *J. Mater. Chem.*, 2011, **21**, 12644.



- 192 N. Chadwick, S. Sathasivam, A. Kafizas, S. M. Bawaked, A. Y. Obaid, S. Al-Thabaiti, S. N. Basahel, I. P. Parkin and C. J. Carmalt, *J. Mater. Chem. A*, 2014, **2**, 5108.
- 193 D. S. Bhachu, D. O. Scanlon, G. Sankar, T. D. Veal, R. G. Egdell, G. Cibir, A. J. Dent, C. E. Knapp, C. J. Carmalt and I. P. Parkin, *Chem. Mater.*, 2015, **27**, 2788–2796.
- 194 M. Takeuchi and K. Maki, *Jpn. J. Appl. Phys.*, 2007, **46**, 7852–7854.
- 195 A. Suzuki and K. Maki, *Chem. Vap. Deposition*, 2006, **12**, 608–613.
- 196 S. O'Brien, K. Linehan, H. Doyle, A. Kingsley, C. Ashfield, B. Frank, L. Xie, K. Leifer, P. Thony, S. Perraud, M. E. Pemble and I. M. Povey, *J. Sol-Gel Sci. Technol.*, 2015, **73**, 666–672.
- 197 *Fluorinated materials for energy conversion*, ed. T. Nakajima and H. Groult, Ms. C. Kreinz, Amsterdam, Boston, MA, 2005.
- 198 N. Hollingsworth, G. A. Horley, M. Mazhar, M. F. Mahon, K. C. Molloy, P. W. Haycock, C. P. Myers and G. W. Critchlow, *Appl. Organomet. Chem.*, 2006, **20**, 687–695.
- 199 N. Hollingsworth, G. Kociok-Köhn, K. C. Molloy and A. L. Sudlow, *Dalton Trans.*, 2010, **39**, 5446.
- 200 H.-J. Cho, K.-W. Park, J.-K. Ahn, N.-J. Seong, S.-G. Yoon, W.-H. Park, S.-M. Yoon, D.-J. Park and J.-Y. Lee, *J. Electrochem. Soc.*, 2009, **156**, J215.
- 201 G. X. Liu, F. K. Shan, J. J. Park, W. J. Lee, G. H. Lee, I. S. Kim, B. C. Shin and S. G. Yoon, *J. Electroceram.*, 2006, **17**, 145–149.
- 202 H. Cachet, A. Gamard, G. Campet, B. Jousseau and T. Toupance, *Thin Solid Films*, 2001, **388**, 41–49.
- 203 K. H. Kim, S. W. Lee, D. W. Shin and C. G. Park, *J. Am. Ceram. Soc.*, 1994, **77**, 915–921.
- 204 R. G. Egdell, W. R. Flavell and P. Tavener, *J. Sol-Gel Sci. Technol.*, 1984, **51**, 345–354.
- 205 E. Elangovan and K. Ramamurthi, *Appl. Surf. Sci.*, 2005, **249**, 183–196.
- 206 R. Buntam, P. Kraisingdecha and W. Sadee, *Adv. Mater. Res.*, 2008, **55–57**, 513–516.
- 207 T. Kololuoma and J. T. Rantala, *Electron. Lett.*, 2000, **36**, 172.
- 208 C. V. Santilli, A. P. Rizzato, S. H. Pulcinelli and A. F. Craievich, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **75**, 205335, DOI: 10.1103/PhysRevB.75.205335.
- 209 E. C. P. E. Rodrigues and P. Olivi, *J. Phys. Chem. Solids*, 2003, **64**, 1105–1112, DOI: 10.1016/S0022-3697(03)00003-9.
- 210 O. Malik, F. J. De la Hidalga-Wade and R. R. Amador, *J. Mater. Res.*, 2015, **30**, 2040–2045.
- 211 N. Noor and I. P. Parkin, *Thin Solid Films*, 2013, **532**, 26–30.
- 212 N. Noor and I. P. Parkin, *J. Mater. Chem. C*, 2013, **1**, 984–996.
- 213 L. Schmidt-Mende and J. L. MacManus-Driscoll, *Mater. Today*, 2007, **10**, 40–48.
- 214 D. S. Bhachu, M. R. Waugh, K. Zeissler, W. R. Branford and I. P. Parkin, *Chem. – Eur. J.*, 2011, **17**, 11613–11621.
- 215 C. K. T. Chew, C. Salcianu, P. Bishop, C. J. Carmalt and I. P. Parkin, *J. Mater. Chem. C*, 2015, **3**, 1118–1125.
- 216 R. Dharmadasa, A. A. Tahir and K. G. U. Wijayantha, *J. Am. Ceram. Soc.*, 2011, **94**, 3540–3546.
- 217 W. A. Farooq, S. M. Ali, J. Muhammad, S. D. Ali, M. H. Aziz, N. Rehman and M. Hussain, *J. Mater. Sci.: Mater. Electron.*, 2013, **24**, 5140–5146.
- 218 S. M. Ali, S. T. Hussain, S. A. Bakar, J. Muhammad and N. Ur Rehman, *J. Phys.: Conf. Ser.*, 2013, **439**, 012013.
- 219 T. Wildsmith, M. S. Hill, A. L. Johnson, A. J. Kingsley and K. C. Molloy, *Chem. Commun.*, 2013, **49**, 8773.
- 220 I. Barbul, A. L. Johnson, G. Kociok-Köhn, K. C. Molloy, C. Silvestru and A. L. Sudlow, *ChemPlusChem*, 2013, **78**, 866–874.
- 221 M. Cargnello, A. Gasparotto, V. Gombac, T. Montini, D. Barreca and P. Fornasiero, *Eur. J. Inorg. Chem.*, 2011, 4309–4323.
- 222 D. Barreca, G. Carraro, V. Gombac, A. Gasparotto, C. Maccato, P. Fornasiero and E. Tondello, *Adv. Funct. Mater.*, 2011, **21**, 2611–2623.
- 223 S. Kaneco, T. Miwa, K. Hachisuka, H. Katsumata, T. Suzuki, S. C. Verma and K. Sugihara, in *Nanocatalysis for Fuels and Chemicals*, ed. A. K. Dalai, American Chemical Society, Washington, DC, 2012, vol. 1092, pp. 25–36.
- 224 F. E. Osterloh, *Nanoscale Effects in Water Splitting Photocatalysis*, Springer Berlin Heidelberg, Berlin, Heidelberg, 2015.
- 225 S. N. Ariffin, H. N. Lim, Z. A. Talib, A. Pandikumar and N. M. Huang, *Int. J. Hydrogen Energy*, 2015, **40**, 2115–2131.
- 226 M. G. Walter, E. L. Warren, J. R. McKone, S. W. Boettcher, Q. Mi, E. A. Santori and N. S. Lewis, *Chem. Rev.*, 2010, **110**, 6446–6473.
- 227 M. Grätzel, *Nature*, 2001, **414**, 338–344.
- 228 S. Choudhary, S. Upadhyay, P. Kumar, N. Singh, V. R. Satsangi, R. Shrivastav and S. Dass, *Int. J. Hydrogen Energy*, 2012, **37**, 18713–18730.
- 229 B. Chen, S. Xiang and G. Qian, *Acc. Chem. Res.*, 2010, **43**, 1115–1124.
- 230 A. M. Azad, S. Larose and S. A. Akbar, *J. Mater. Sci.*, 1994, **29**, 4135–4151.
- 231 H. Weidong, Q. Wei, W. Xiaohong, D. Xianbo, C. Long and J. Zhaohua, *Thin Solid Films*, 2007, **515**, 5362–5365.
- 232 K. Gurunathan, *Int. J. Hydrogen Energy*, 2004, **29**, 933–940.
- 233 G. Sarala Devi, S. V. Manorama and V. J. Rao, *Sens. Actuators, B*, 1999, **56**, 98–105, DOI: 10.1016/S0925-4005(99)00164-1.
- 234 B. H. Park, B. S. Kang, S. D. Bu, T. W. Noh, J. Lee and W. Jo, *Nature*, 1999, **401**, 682–684.
- 235 P.-F. Zhuang, T. Liu, X.-H. Xie, C. He and C.-Y. Duan, *Dalton Trans.*, 2015, **44**, 464–467.
- 236 C. Michel, M. Hervieu, M. M. Borel, A. Grandin, F. Deslandes, J. Provost and B. Raveau, *Z. Phys. B: Condens. Matter*, 1987, **68**, 421–423.
- 237 M. Mehring, *Coord. Chem. Rev.*, 2007, **251**, 974–1006.
- 238 M. A. Matchett, M. Y. Chiang and W. E. Buhro, *Inorg. Chem.*, 1990, **29**, 358–360.
- 239 M.-C. Massiani, R. Papiernik, L. G. Hubert-Pfalzgraf and J.-C. Daran, *Polyhedron*, 1991, **10**, 437–445.



- 240 C. Knispel, C. Limberg and B. Ziemer, *Inorg. Chem.*, 2010, **49**, 4313–4318.
- 241 P. A. Williams, A. C. Jones, M. J. Crosbie, P. J. Wright, J. F. Bickley, A. Steiner, H. O. Davies, T. J. Leedham and G. W. Critchlow, *Chem. Vap. Deposition*, 2001, **7**, 205.
- 242 S. J. A. Moniz, C. S. Blackman, C. J. Carmalt and G. Hyett, *J. Mater. Chem.*, 2010, **20**, 7881.
- 243 S. J. A. Moniz, D. Bhachu, C. S. Blackman, A. J. Cross, S. Elouali, D. Pugh, R. Quesada Cabrera and S. Vallejos, *Inorg. Chim. Acta*, 2012, **380**, 328–335.
- 244 S. D. Cosham, M. S. Hill, G. A. Horley, A. L. Johnson, L. Jordan, K. C. Molloy and D. C. Stanton, *Inorg. Chem.*, 2014, **53**, 503–511.
- 245 L. M. Peter, K. G. U. Wijayantha, D. J. Riley and J. P. Waggett, *J. Phys. Chem. B*, 2003, **107**, 8378–8381.
- 246 S. J. A. Moniz, R. Quesada-Cabrera, C. S. Blackman, J. Tang, P. Southern, P. M. Weaver and C. J. Carmalt, *J. Mater. Chem. A*, 2014, **2**, 2922.
- 247 A. McInnes, J. S. Sagu and K. G. U. Wijayantha, *Mater. Lett.*, 2014, **137**, 214–217.
- 248 P. Brack, J. S. Sagu, T. A. N. Peiris, A. McInnes, M. Senili, K. G. U. Wijayantha, F. Marken and E. Selli, *Chem. Vap. Deposition*, 2015, **21**, 41–45.
- 249 S. J. Hong, S. Lee, J. S. Jang and J. S. Lee, *Energy Environ. Sci.*, 2011, **4**, 1781.
- 250 J. R. McKone, N. S. Lewis and H. B. Gray, *Chem. Mater.*, 2014, **26**, 407–414.
- 251 A. Tricoli, M. Righettoni and A. Teleki, *Angew. Chem., Int. Ed.*, 2010, **49**, 7632–7659.
- 252 M. M. Arafat, B. Dinan, S. A. Akbar and A. S. M. A. Haseeb, *Sensors*, 2012, **12**, 7207–7258.
- 253 L. Filipovic and S. Selberherr, *Sensors*, 2015, **15**, 7206–7227.
- 254 E. Comini, *Sensors*, 2013, **13**, 10659–10673.
- 255 F. E. Annanouch, S. Vallejos, T. Stoycheva, C. Blackman and E. Llobet, *Thin Solid Films*, 2013, **548**, 703–709.
- 256 L. G. Bloor, J. Manzi, R. Binions, I. P. Parkin, D. Pugh, A. Afonja, C. S. Blackman, S. Sathasivam and C. J. Carmalt, *Chem. Mater.*, 2012, **24**, 2864–2871.
- 257 S. Das and V. Jayaraman, *Prog. Mater. Sci.*, 2014, **66**, 112–255.
- 258 T. T. Stoycheva, S. Vallejos, R. G. Pavelko, V. S. Popov, V. G. Sevastyanov and X. Correig, *Chem. Vap. Deposition*, 2011, **17**, 247–252.
- 259 J. Zhao, S. Wu, J. Liu, H. Liu, S. Gong and D. Zhou, *Sens. Actuators, B*, 2010, **145**, 788–793.
- 260 N. P. Chadwick, S. Sathasivam, S. M. Bawaked, M. Mokhtar, S. A. Althabaiti, S. N. Basahel, I. P. Parkin and C. J. Carmalt, *J. Mater. Chem. A*, 2015, **3**, 4811–4819.
- 261 N. Noor, C. K. T. Chew, D. S. Bhachu, M. R. Waugh, C. J. Carmalt and I. P. Parkin, *J. Mater. Chem. C*, 2015, **3**, 9359–9368, DOI: 10.1039/C5TC02144H.
- 262 D. S. Bhachu, D. O. Scanlon, E. J. Saban, H. Bronstein, I. P. Parkin, C. J. Carmalt and R. G. Palgrave, *J. Mater. Chem. A*, 2015, **3**, 9071–9073.
- 263 D. S. Bhachu, S. Sathasivam, C. J. Carmalt and I. P. Parkin, *Langmuir*, 2014, **30**, 624–630.
- 264 P. Kevin, S. N. Malik, M. A. Malik and P. O'Brien, *Mater. Lett.*, 2015, **152**, 60–64.
- 265 S. S. Meysami, A. A. Koós, F. Dillon, M. Dutta and N. Grobert, *Carbon*, 2015, **88**, 148–156.
- 266 D. S. Bhachu, S. Sathasivam, G. Sankar, D. O. Scanlon, G. Cibin, C. J. Carmalt, I. P. Parkin, G. W. Watson, S. M. Bawaked, A. Y. Obaid, S. Al-Thabaiti and S. N. Basahel, *Adv. Funct. Mater.*, 2014, **24**, 5075–5085.

