

CrossMark
click for updatesCite this: *Chem. Sci.*, 2016, 7, 855

Topochemical molten salt synthesis for functional perovskite compounds

Lihong Li,^{ab} Jinxia Deng,^a Jun Chen^a and Xianran Xing^{*a}

A topochemical molten salt synthesis (TMSS) method, which is rapid and a modification of the molten salt synthesis method (MSS), to facilitate crystal growth with improved phase-purity and particle homogeneity, is one of the strategic approaches aimed at a controllable morphology synthesis. The TMSS method is an environmentally friendly and mild way to prepare pure and controllable perovskites, which are famous functional materials, used as piezoelectrics, catalysts, ferroelectrics, multiferroics, and negative thermal expansion compounds, at a moderate reaction temperature in a short soaking time. This report reviews various TMSS reactions and their applications in fulfilling the demand for the tunable morphology of perovskite materials, such as one dimensional, two dimensional and three dimensional perovskites in molten salts, which mainly include: piezoelectrics, photocatalysts, negative thermal expansion matters and other functional perovskites. The double and layered perovskites obtained by TMSS methods are also discussed. We believe that a comprehensive understanding of the TMSS method for functional perovskites will definitely promote the development of a clean, efficient and tunable production process for advanced functional materials.

Received 18th September 2015
Accepted 16th October 2015

DOI: 10.1039/c5sc03521j

www.rsc.org/chemicalscience

1 Introduction

Due to the advancements in modern technology, the study of molten salt synthesis (MSS) has achieved considerable progress, and lots of salts have been found by chemists.^{1,2} MSS is one of

the important issues especially for materials science. Salt melts have a long history as a solvent in research as well as in industry due to their low toxicity, low cost, low vapour pressure, abundant availability, high heat capacity, large electrochemical window, and high ionic conductivity.³ They have been used as reaction media for various organic and inorganic reactions, and also as the flux for crystal growth. Although, in previous studies, great success has been achieved in the study of the reaction mechanism of MSS and the nature of the salts, it still remains a challenge to extend the method to control the morphology of the target sample due to the difficult shape-control of the product in the high temperature molten salts.

^aDepartment of Physical Chemistry, University of Science and Technology Beijing, Beijing 100083, China. E-mail: Xing@ustb.edu.cn

^bKey Laboratory of Green Printing, Institute of Chemistry, Chinese Academy of Sciences (ICCAS), Beijing Engineering Research Center of Nanomaterials for Green Printing Technology, Beijing National Laboratory for Molecular Sciences (BNLMS), Beijing 100190, China



Lihong Li received her BS degree from Wuhan University of Science and Technology in June 2005 and her PhD from the University of Science and Technology Beijing (USTB) in Jan 2011. She carried out her post-doctoral research in the Tsinghua University, in 2011. She is now an associate professor of the Institute of Chemistry, Chinese Academy of Sciences.

Her research interests are inorganic functional materials, materials chemistry, the molten salt method, and green printing of nano functional ink.



Jinxia Deng is an associate professor at the Department of Chemistry, University of Science and Technology Beijing (USTB). She received her BS and PhD at USTB in 2002 and 2008, respectively. Her research concerns the synthesis and characterization of functional solid compounds by the molten salt method. Recently, she has been focusing on impedance spectroscopy and negative

thermal expansion (NTE) for perovskite complex oxides and the reaction mechanism in hydrometallurgical processes for minerals.



The topochemical molten salt synthesis (TMSS) method is a kind of modification of the MSS method. It is one of the environmentally friendly and mild ways to prepare pure and morphologically-controllable samples at a moderate temperature in a short soaking time. The morphology of the products can inherit that of the major solid-state raw materials *via* TMSS, that is, the shape and size of the as-synthesized compounds can be controlled by an appropriate choice of raw materials, salts, sintering temperature and reaction time. The TMSS method has the advantages of combining the molten salt method and the topochemical method, associated with the use of localized solid-state compound transformations *via* the exchange, deletion, or insertion of individual atoms.⁴

Perovskites, a kind of famous functional materials, with potential as piezoelectrics, catalysts, multiferroics, solar cells and negative thermal expansion materials, have aroused much attention.⁵ However, a high synthesis temperature and long reaction time are usually needed to obtain them. Meanwhile, it is reported that they have unique shape-dependent properties, and many experimental efforts have been made to prepare hollow spheres, tubes, rods, and wires, as well as sheets and platelets. The TMSS gives us a useful strategy to modify the properties of the functional perovskite materials by being dependent on the nature of both of the salts and the raw materials. The TMSS's low reaction temperature, short reaction time, tunable morphology allows a broad range of inorganic crystalline perovskites to be obtained. It is interesting to systematically discuss the TMSS method for the controllable morphology of functional perovskite compounds and the effect of the raw materials. The study on topochemical molten salt synthesizing for functionalized perovskite compounds is a new topic especially in the discipline of materials chemistry. It is timely to review the achievements and promote the development of TMSS applications for the future.^{6,7}

In the present review, various TMSS reactions and their applications in fulfilling the demand for tunable morphology perovskite materials, such as one dimensional, two dimensional and three dimensional perovskites in molten salts, are summarized and discussed. It should be noted that the dimension/microstructure of the target sample is inherited from the different fusing of the raw materials. Meanwhile, the functional perovskites, which mainly include: piezoelectrics, photocatalysts, negative thermal expansion compounds and other functional perovskites, obtained from the TMSS method are expounded upon, with the purpose of providing a brief overview of the topochemical molten salt synthesis method and its influence on the energy efficiency, chemical composition or microstructure of the functional perovskite materials. In addition, the double and layered perovskites obtained by the TMSS methods and the perovskites synthesized by low temperature TMSS methods are also discussed. In the end, the possible further applications of the TMSS method for perovskites are predicted. We believe that a comprehensive understanding of the TMSS method for functional perovskites will definitely promote the development of a clean, efficient and tunable production process for advanced functional materials.

2 Morphology of perovskite compounds controlled by TMSS

2.1 The mechanism and method of the TMSS process

The synthesis of nanoscale structures with special morphologies has attracted extensive attention in the past two decades as a result of their novel size-dependent properties. Intense experimental efforts have been spent on preparing nanoparticles, nanowires, nanotubes, nanoplatelets and three dimensional particles of nanostructures.⁸ The use of different types of "fluxes", including low melting metals and salts, has in fact been extensively explored for the synthesis of metallic and



Jun Chen received his BS degree from Hefei University of Technology in June 2001 and PhD from the University of Science and Technology Beijing (USTB) in March 2007. He is now a full professor of the Department of Physical Chemistry, USTB. He carried out his postdoctoral research in the TU-Darmstadt, Germany, in 2008, supported by the Alexander von Humboldt Fellowship. His research inter-

ests are solid-state chemistry, negative thermal expansion, and inorganic functional materials.



Xianran Xing is Changjiang professor at the University of Science and Technology Beijing (USTB), Chairperson in the Department of Physical Chemistry USTB, and Fellow of the Royal Society of Chemistry (FRSC). He received his BS in Chemistry from An'qin Teachers College in June 1988 and PhD in physical chemistry from USTB in March 1994. His research interests focus on the study of solid

state chemistry, involving chemical synthesis strategies, crystal structure and chemical design for functional materials. Over the past twelve years, he has led a group working on negative thermal expansion (NTE) in perovskite compounds and topochemical molten salt synthesis for functional perovskite compounds. He has published more than one hundred peer reviewed papers.



Table 1 A summary of different dimensional perovskites synthesized by the TMSS method and their templates

Dimensionality	Materials	Template	Molten salts	Reference
1D	NaNbO ₃	K ₂ Nb ₈ O ₂₁ nanowires	NaCl	24
		Nb ₂ O ₅ nanorods	NaCl	25
	KNbO ₃	Nb ₂ O ₅ nanorods	KCl	25
		Nb ₂ O ₅ nanowires	LiCl	26
	(K,Na)NbO ₃	Nb ₂ O ₅ nanorods	KCl	25 and 27–30
	BaTiO ₃	TiO ₂ nanorods	NaCl–KCl (1 : 1 mol)	31
		H ₂ Ti ₃ O ₇ nanowires	Ba(OH) ₂	32–35
	PbTiO ₃	TiO ₂ rods	NaCl–KCl (1 : 1 mol)	36 and 37
		BaTiO ₃	BaBi ₄ Ti ₄ O ₁₅ platelets	NaCl–KCl (1 : 1 mol)
	2D	SrTiO ₃	SrBi ₄ Ti ₄ O ₁₅ platelets	KCl
CaTiO ₃		CaBi ₄ Ti ₄ O ₁₅ platelets	KCl	40
Ba _{1–3} Ca _x TiO ₃		Bi ₄ Ti ₃ O ₁₂ platelets	NaCl–KCl (1 : 1 mol)	41
Na _{0.5} Bi _{0.5} TiO ₃		Na _{0.5} Bi _{4.5} Ti ₄ O ₁₅ platelets	NaCl–KCl (1 : 1 mol)	42 and 43
NaNbO ₃		Bi _{2.5} Na _{3.5} Nb ₅ O ₁₈ platelets	NaCl	44–47
		Na _{3.5} Bi _{2.5} Nb ₅ O ₁₈ platelets	NaCl	7, 44 and 48
KNbO ₃		K ₄ Nb ₆ O ₁₇ platelets	KCl	49 and 50
		Nb ₂ O ₅ platelets	KCl	51
(Na _{0.5} K _{0.5})NbO ₃		K ₄ Nb ₆ O ₁₇ platelets	KCl	17
AgSbO ₃		NaSbO ₃ nanoplates	AgNO ₃	52
Ag ₂ [Ca _{1.5} M ₃ O ₁₀] (M = Nb, Ta)		Li ₂ [Ca _{1.5} M ₃ O ₁₀] (M = Nb, Ta)	AgNO ₃	53
AgLaNb ₂ O ₇		RbLaNb ₂ O ₇	AgNO ₃	8 and 54
Ag ₂ Nb ₃ O ₁₀ (A = Ca, Sr)		RbA ₂ Nb ₃ O ₁₀ (A = Ca, Sr)	AgNO ₃	46 and 55
PbTiO ₃		PbBi ₄ Ti ₄ O ₁₅	KCl	7
0.4(Na _{1/2} Bi _{1/2})TiO ₃ –0.6PbTiO ₃		PbBi ₄ Ti ₄ O ₁₅	NaCl	56
3D		KNbO ₃	Nb ₂ O ₅ hollow nanospheres	KCl
	LaMnO ₃	Porous spherical Mn ₂ O ₃	NaNO ₃ –KNO ₃ (2 : 1 mol)	59
	ZnEu ₂ Ti ₃ O ₁₀	K ₂ Eu ₂ Ti ₃ O ₁₀	ZnCl ₂	60
	AEu ₂ Ti ₂ NbO ₁₀ (A = Na, Li)	CsEu ₂ Ti ₂ NbO ₁₀	Alkali nitrates	60

lengths of several micrometers, show a bundlelike morphology, which is characteristic of the starting K₂Nb₈O₂₁ nanowires template. The phase of the obtained sodium niobate was determined to be orthorhombic NaNbO₃ (JCPDS 33-1270), with lattice parameters of $a = 0.5569$, $b = 1.5123$, and $c = 0.5505$ nm.

2.3 Two dimensional morphology

Two dimensional materials are materials in which the electron only has free movement in two dimensions, such as thin films, super lattices and quantum wells. The discovery of graphene largely promoted the development of 2D materials, and many researchers focus on the 2D materials used in solar cells, piezoelectric materials, *etc.*⁶⁴ Recently, many efforts have been made to synthesize low dimensional perovskites, through techniques such as hydrothermal and molten salt synthesis (MSS), but the platelet perovskite particles are still not easily obtained due to the nature of regular-perovskite structured materials which typically grow as equiaxed particles. The TMSS method gives a route to obtain the 2D perovskites.^{44,65} For example, Saito *et al.* used the TMSS method to obtain plate-like NaNbO₃ particles as templates for (001) oriented (K,Na)NbO₃-based ceramics (Fig. 3). Firstly, a Bi_{2.5}Na_{3.5}Nb₅O₁₈ (BiNN5) platelet was synthesized at 1100 °C using molten NaCl salt as a flux. Then, using a TMSS reaction, a NaNbO₃ platelet was synthesized from the BiNN5 and a complementary reactant, Na₂CO₃, in a NaCl flux at 950 °C. The by-product, Bi₂O₃, was removed. The synthesized NaNbO₃ had the same morphology as

BiNN5, a 0.5 mm thickness and 10–15 mm side length in a developed area, and consisted of a single-phase with the 001 plane of perovskite, identified by JCPDS powder diffraction file card no. 33-1270.⁴⁴ The formation of the platelet NaNbO₃ might be as follows:



2.4 Three dimensional morphology

Materials with three dimensional morphologies, including composites consisting of one or more basic structural units in zero dimensional, one-dimensional, two-dimensional or porous materials, such as hollow spheres,⁵⁰ nickel foam⁶⁶ *etc.*, have aroused much attention in the academic community and industry due to their unique microstructures and singular properties. The TMSS method has been used to obtain perovskites with 3D morphologies, for example, porous spherical and cubic LaMnO₃ from porous Mn₂O₃ precursors in a mixture of NaNO₃ and KNO₃.⁵⁹ There is another example, in which Xing *et al.* obtained KNbO₃ hollow spheres from Nb₂O₅ hollow spheres *via* the TMSS method (Fig. 4).⁵⁷ In the KCl molten salt, K⁺ needed to diffuse inside the T-Nb₂O₅ hollow spheres, and this process involved bond-breaking, rebonding, and the generation of new bonds. Viewed along the c axis of Nb₂O₅, the NbO₆ and NbO₇ units were corner-sharing, and in the perovskite KNbO₃ crystal, the NbO₆ octahedron units connected



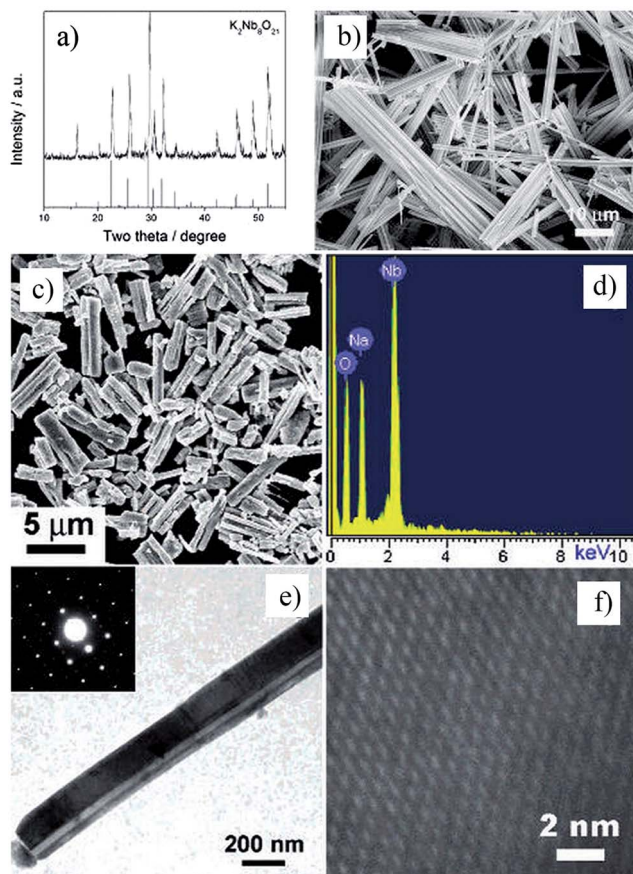


Fig. 2 (a) XRD and (b) SEM images of the potassium niobate nanowires. The angles for the standard sample of potassium niobate are shown in the lower part of panel a. (c) SEM image of sodium niobate nanorods. (d) EDX spectrum showing the complete conversion from K niobate to Na niobate. (e) TEM image of an individual sodium niobate nanorod. Inset is the corresponding SAED pattern. (f) High-resolution TEM image of the same nanorod shown in panel e (ref. 32 Copyright 2007, American Chemical Society).

with shared corners along the *a*, *b*, and *c* axes. Therefore, although the small rods of the shell became cubelike, due to the high thermal stability of the Nb_2O_5 hollow nanospheres and the compatibility of the structure of the Nb_2O_5 and KNbO_3 , the morphology of the hollow spheres could be kept and KNbO_3 hollow nanospheres were obtained.

3 Various functional perovskites synthesized by TMSS

The ABO_3 family with perovskite structure has aroused a broad interest since it was investigated in the 1970s.⁶⁷ They have important applications in fields such as piezoelectrics, photocatalysis, ferroelectrics, multiferroics, and negative thermal expansion materials (NTE).⁶⁸ The synthesis of these functional perovskites in the form of nano/micro crystalline powders and defined nanoscale architectures has been realized in different TMSS systems. Depending on the nature of the TMSS, low temperatures, short times, tunable morphologies, controllable

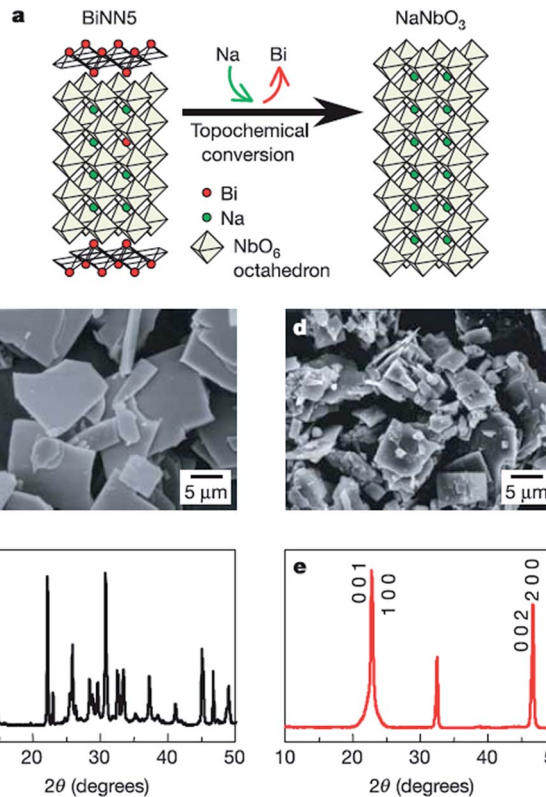


Fig. 3 Schematic diagram of topochemical conversion from the bismuth layered structure BiNN_5 particles to plate-like NaNbO_3 particles. (a) Crystal structures of the plate-like BiNN_5 and NaNbO_3 particles. (b and c) An SEM image and the X-ray diffraction profile of the plate-like BiNN_5 particles used as the precursor. (d and e) An SEM image and the X-ray diffraction profile of the plate-like NaNbO_3 particles. The X-ray diffraction profile of the NaNbO_3 particles is characterized by pseudo-tetragonal Miller indices. The BiNN_5 particles are completely converted into the regular perovskite-structured NaNbO_3 particles with a preserved plate-like shape (ref. 25 Copyright 2004 Nature Publishing Group.).

stoichiometric ratios, and a broad range of inorganic crystalline structures of functional perovskites can be achieved.

3.1 Piezoelectric perovskites synthesized by TMSS

Piezoelectric materials can produce an electric field upon mechanical deformation, and form mechanical deformation *via* the effect of the electric field.^{24,44,69} The inherent mechanical electric coupling effect means piezoelectric materials have been widely used in nanometer generators,⁷⁰ flexible nanocomposite generators (Fig. 5),^{71,72} sensors,⁶⁸ actuators,⁷³ and other electronic devices.^{74,75} Due to their significant piezoelectric properties the perovskite-type piezoelectric materials such as, $\text{Pb}(\text{Zr},\text{Ti})\text{O}_3$ (PZT),^{76,77} $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ (BNT),^{69,78} $(\text{K},\text{Na})\text{NbO}_3$ (KNN),^{44,72} and BaTiO_3 (BT)⁷² based materials, arouse widespread interest. The piezoelectric properties are largely affected by the morphology and structure of the materials (Fig. 5a–e),^{45,71} and the piezoelectric properties and morphology of the compounds can be tailored by the TMSS method. For example, the NaNbO_3 platelet, synthesized by the TMSS method, is used





Fig. 4 Formation processes and structure evolution of the KNbO_3 hollow spheres and Nb_2O_5 solid spheres. The insets are the Nb_2O_5 hollow spheres and the KNbO_3 hollow spheres (ref. 31 Copyright 2013, the Royal Society of Chemistry).

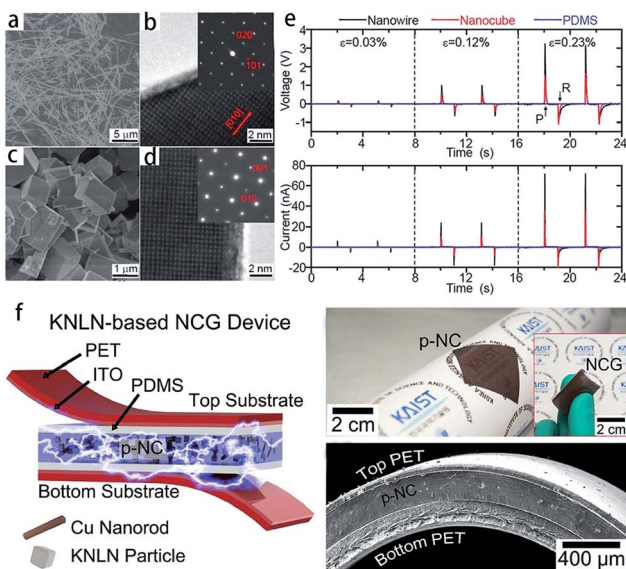


Fig. 5 SEM and TEM images of NaNbO_3 nanowires (a and b) and nanocubes (c and d). (e) Power generation of NaNbO_3 nanowire-based (black lines) and nanocube-based (red lines) NGs at a given compressive strain. The top image is the open circuit voltage and below is the closed circuit current. PDMS itself (blue lines) does not show any signals. Here, ϵ , P , and R are for the strain value, press, and release, respectively. (f) Schematic of a flexible nanocomposite generator (NCG) device using $0.942(\text{K}_{0.480}\text{Na}_{0.535})\text{NbO}_3-0.058\text{LiNbO}_3$ (KNLN) particles and Cu NRs. Photograph of the flexible p-NC layer attached to a rolled paper. The inset shows the final NCG device bent by fingers (ref. 71 Copyright 2014, 2011 American Chemical Society and ref. 72 Copyright 2014, WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim).

as a reactive template for textured $(\text{K},\text{Na})\text{NbO}_3\text{-LiTaO}_3\text{-LiSbO}_3$ polycrystals synthesized by the reactive-templated grain growth (RTGG) method which exhibit a high piezoelectric constant d_{33} of 416 pC N^{-1} .⁴⁴ Rod-like ANbO_3 ($A = \text{K}, \text{Na}, (\text{Na},\text{K})$) were fabricated by a TMSS method, shown in Fig. 6.²⁵ The process is as follows: first, the precursor KNb_3O_8 with a rod structure was prepared under the conditions of a KCl molten salt environment at 800°C for 3 h. Then, rod-like $\text{H}_3\text{ONb}_3\text{O}_8$ and Nb_2O_5 were obtained from the rod-like KNb_3O_8 precursor. Finally, the rod-like ANbO_3 ($A = \text{K}, \text{Na}, (\text{Na},\text{K})$) were achieved *via* the intermediate oxide Nb_2O_5 . The rod-like structure of the final



Fig. 6 (a) Schematic illustration of the structural transformations of the Nb-containing species along with the mechanism of KNbO_3 synthesis by TMSS treatment. (b) An XRD pattern of the Nb_2O_5 particles obtained from the rodlike $\text{H}_3\text{ONb}_3\text{O}_8$ particles. The inset is an SEM micrograph of the Nb_2O_5 particles. (c) TEM image of the Nb_2O_5 rods with (inset) a typical SEAD pattern obtained from the rods. (d–f) XRD patterns of the KNbO_3 particles obtained from different precursors KNb_3O_8 , $\text{H}_3\text{ONb}_3\text{O}_8$ and Nb_2O_5 , respectively. (g) TEM image of an isolated KNbO_3 rod obtained from the precursor Nb_2O_5 particles with (inset) its corresponding SEAD pattern. (h) The piezoelectric constant d_{33} of the $(\text{Na},\text{K})\text{NbO}_3$ ceramic is 140 pC N^{-1} , and the SEM image of the surface of the ceramic (ref. 33 Copyright 2009, American Chemical Society).





product can only be achieved when using the rod-like Nb_2O_5 precursor. The structural evolution investigated among protonic niobate, niobium oxide, and niobates, shows that the similar structure (three NbO_6 octahedra connected with shared corners and edges along the [001] direction) is the key to maintaining the morphology of the precursor. The $(\text{Na,K})\text{NbO}_3$ ceramic sintered from the as-prepared rodlike particles under pressureless conditions in air performed with a high piezoelectricity ($d_{33} = 140 \text{ pC N}^{-1}$), which is much better than that of the ceramics obtained from cubic or spherical particles ($d_{33} = 97 \text{ pC N}^{-1}$).²⁵


The reaction of the rod-like KNb_3O_8 might be as follows: first, the Nb_2O_5 and KCl were reacted to produce KNb_3O_8 . Then an ion exchange of the K^+ ion by the hydronium ion was observed according to the reaction:



Afterward, the $\text{H}_3\text{ONb}_3\text{O}_8$ was heated to remove H_2O , which is depicted as follows:



The reaction for the formation of the KNbO_3 rods from the rodlike Nb_2O_5 particles is as follows:



3.2 Photocatalysis perovskites synthesized by TMSS

Current synthetic challenges for the crystal growth of complex oxides can be addressed by utilizing TMSS methods, which have made a significant impact in research involving solar energy conversion.^{30,52,79} The improved phase-purity and particle homogeneity is in favour of enhancing photocatalytic properties. Early investigations into the photocatalytic activities of metal oxides utilized only high-temperature 'grind and heat' solid state syntheses to obtain the desired products.⁸⁰ Starting with the research of the Maggard group, the MSS of metal-oxide photocatalysts has been used increasingly to understand the impact of the particle sizes, morphologies, and the surface.^{81,82} The TMSS preparation of perovskites has been of increasing importance in a growing number of studies probing photocatalytic mechanisms and the surface reactivities of photocatalysts, such as AgSbO_3 ,⁵² LaMnO_3 ,⁵⁹ KNbO_3 (ref. 57) and AgTaO_3 , AFeO_3 ($\text{A} = \text{Bi, La, Ln}$), and $\text{Bi}(\text{Mg}_{3/8}\text{Fe}_{2/8}\text{Ti}_{3/8})\text{O}_3$.⁸³ For example, AgSbO_3 visible-light photocatalysts were synthesized from NaSbO_3 nanoplates, which were prepared by salt-assisted aerosol combustion, *via* the TMSS method (Fig. 7).⁵² It was revealed that the surface chemistry and particle morphology influenced the photocatalytic activity. Visible-light-induced photodegradation of RhB was selected as the model reaction to evaluate the photocatalytic properties of the different AgSbO_3

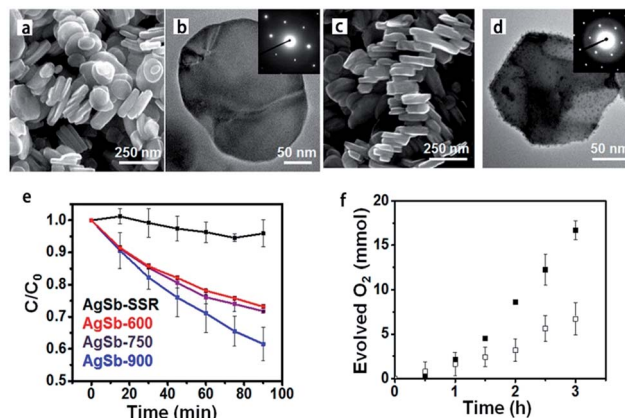


Fig. 7 (a) SEM and (b) TEM images of the NaSbO_3 product obtained from an aerosol-assisted synthesis. (c) SEM and (d) TEM images of the AgSbO_3 , single-crystalline NaSbO_3 plates in molten AgNO_3 were used as the template. (e) Rhodamine B photocatalytic degradation under $\lambda = 400\text{--}500 \text{ nm}$ illumination. (f) Oxygen evolution in the presence of 0.1 M AgNO_3 (ref. 55 Copyright 2015, American Chemical Society).

samples. AgSbO_3 prepared *via* the TMSS route exhibited a greater photoactivity for the photodegradation of RhB in comparison to the AgSbO_3 synthesized from the other method (Fig. 7e). It can be predicted that further modifications of the TMSS methods for tuning particle sizes, morphologies, and specific surface areas could be used to obtain other nano perovskites with highly desired optical and photocatalytic properties in future.

3.3 Negative thermal expansion (NTE) perovskites synthesized by TMSS

The thermal expansion compatibility of different components is one of the key problems for modern devices, such as thin films, multilayer chip capacitors (MLCCs), solid oxide fuel cells, thermoelectric materials, and high temperature piezoelectrics. Thermal stress could give rise to device failure due to an undesirable mismatch of the coefficients of thermal expansion (CTE). The design of highly reliable devices should pay enough attention to the control of thermal expansion, which is extremely difficult, but an important topic. The size effect brings about unexpected phenomena upon thermal expansion. With decreasing particle sizes, NTE can be produced in those compounds which have normal thermal expansion in the bulk state, such as magnetic nanoparticles.⁸⁴ Moreover, giant NTE of ferroelectrics is lost and transformed to a positive thermal expansion, as particle size decreases. The development of TMSS can reveal the nature of NTE perovskites as the particle size, stoichiometric ratio and dispersity can be controlled *via* this chemical method. Perovskite type NTE materials were synthesized by the TMSS method, for example PbTiO_3 (ref. 36) and PbTiO_3 -based materials.⁵⁶ It should be mentioned that the effect of size on thermal expansion is just beginning to be studied. More interesting results will appear, and the research in this field is significant for the development of devices, as the nano/micro materials for devices become important.⁸⁴





Fig. 8 (Top) Electron density plot of $A'_2[La_{(n-1)}Ti_nO_{(3n+1)}]$ and $Ag_2-LnTi_3O_{10}$. (a and b) FESEM images of solid-state prepared $Rb_2La_2Ti_3O_{10}$. (c and d) Silver-exchanged $Ag_2La_2Ti_3O_{10}$ in $AgNO_3$ flux (ref. 30 Copyright 2013, American Chemical Society).

3.4 Other functional perovskites synthesized by TMSS

Other functional perovskites, such as multiferroic materials, catalysts *etc.* are also prepared *via* the TMSS method. For perovskite-type multiferroic materials, they have potential applications for new types of electronic devices, such as ferroelectrics, multiple-state memories and new data-storage media.^{85–87} The synthesis method used to obtain the desired nanostructures is crucial for exploiting nanoscale electric, magnetic, and thermal properties. For example, for the multiferroic $BiFeO_3$ -based material, the limited available information relating to the size dependence of the physical properties is mainly due to the difficulty in preparing the pure $BiFeO_3$ -based material.⁸⁸ During the synthesis of $BiFeO_3$, the kinetics of the phase formation in the $Bi_2O_3-Fe_2O_3$ system can easily lead to the appearance of impurity phases, such as $Bi_{2.5}FeO_{4.0}$ and $Bi_2Fe_4O_9$. The TMSS is an appropriate and rapid method for such materials. Not only high purity samples, but also samples with controllably sized particles can be obtained.^{86,89} Perovskite-type catalysts, are promising automotive exhaust catalysts⁹⁰ for the catalytic removal of VOCs⁵⁹ *etc.* due to their surface redox properties, high bulk oxygen mobility and good thermal stability. The morphology and surface area have a great impact on the performance of catalysts. For example, the porous spherical and cubic $LaMnO_3$ with a high activity for the catalytic

removal of toluene was produced in a morphologically controlled synthesis *via* the TMSS method from the porous spherical M_2O_3 .⁵⁹

4 Double and layered perovskites synthesized by TMSS

Double perovskite oxides with the general formula $AA_0BB_0O_6$ (where A and A_0 are rare earth or alkaline earth metals, and B and B_0 are d-block transition metals) display a wide variety of interesting physical properties that vary with changes in their composition. Considerable research is being carried out to explore new double perovskite materials, to understand the origin of their properties (*e.g.* magnetodielectric, magnetoresistance, and magneto-capacitance), to improve their properties, and to adapt the materials to produce technology for each application. The nanostructure of double perovskites can significantly enhance their properties. To obtain nanostructures, such as, La_2CoMnO_6 , La_2NiMnO_6 , $Ca_2Fe_{0.8}Co_{0.2}MoO_6$, the TMSS method has been applied due to the tunable morphology and the controllable stoichiometric ratio.^{89,91,92}

Members of the Dion–Jacobson family of layered perovskites,^{93–95} $A[A'_{n-1}B_nO_{3n+1}]$ (A = alkali, A' = alkaline earth or rare earth, B = transition metal), have an equal number of A(A') and B cations, so they are ideal precursors to nondefective, three dimensional (3D) perovskites of the general formula $AA'_{n-1}B_nO_{3n}$.⁶⁰ For example, $ZnEu_2Ti_3O_{10}$ was prepared by ion-exchanging $K_2Eu_2Ti_3O_{10}$ in molten $ZnCl_2$. $AEu_2Ti_2NbO_{10}$ (A = Na, Li) compounds were prepared from $CsEu_2Ti_2NbO_{10}$ in the molten alkali nitrates. The conversion of a Dion–Jacobson layered perovskite $A[A'_{n-1}B_nO_{3n+1}]$ to a 3D perovskite $AA'_{n-1}B_nO_{3n}$ requires that either the A, A', or B ion be reducible.⁶⁰ Furthermore, it is well known that the photocatalytic efficiency of a given semiconductor photocatalyst depends on three physical processes, including the light absorption, the transport of the charge carriers and the recombination of the photo-generated electron–hole pairs. The electronic band structure plays a critical role in the above processes. Furthermore, it was found that the electronic band structure of layered perovskites is able to be engineered.⁹⁶ Boltersdorf *et al.* systematically reported that $Ag_2La_2Ti_3O_{10}$, and $AgLaNb_2O_7$, $Ag_2Nb_3O_{10}$ (A = Ca, Sr) were prepared by the TMSS method using solid-state prepared $Rb_2La_2Ti_3O_{10}$ in $AgNO_3$ salts (Fig. 8), and it was found that the silver-exchanged $Rb_2La_2Ti_3O_{10}$ layered structures exhibited the highest photocatalytic hydrogen formation rates under ultraviolet and visible irradiation ($\sim 13\ 616\ \mu\text{mol H}_2\ \text{g}^{-1}\ \text{h}^{-1}$).⁵⁵

5 Conclusions and outlook

Synthesizing materials with the desired morphology and phase purity in a reproducible and environmentally friendly manner is arousing considerable attention in materials science all over the world. After two decades of studies on the topic of TMSS, there has been great progress in aspects of new TMSS processes for different perovskites. The new interdisciplinary field of TMSS



for perovskites has been reviewed. The mechanism of the TMSS method is also presented. The properties, such as, piezoelectric, photocatalytic, negative thermal expansion *etc.*, and the different morphologies of perovskite compounds could be tailored by the TMSS method. Meanwhile, the double and layered perovskites can also be obtained by TMSS methods with a tunable morphology and a controllable stoichiometric ratio.

For future applications of TMSS in perovskites, there still exist some problems which have to be considered. For example, the solubility of different precursors and the understanding of the growth mechanisms of perovskites are still not fully developed; improved understanding of the chemical and physical properties and the crystal structures of the materials is called for. Further study of the TMSS method for tuning particle morphologies, size and crystallinity can be used to obtain other target morphologies of perovskites that are doped or have highly desirable piezoelectric, photocatalytic, negative thermal expansion properties *etc.* In addition, not limited to the preparation of perovskites, the TMSS method can be extended to obtain other kinds of functional materials, for example, a high voltage layered $\text{Li}_{1.2}\text{Ni}_{0.16}\text{Co}_{0.08}\text{Mn}_{0.56}\text{O}_2$ cathode material with a hollow spherical structure has been synthesized by the TMSS method in a NaCl flux from MnO_2 hollow spheres.⁹⁷ The development of lower melting temperature molten salts (ionic liquids) for the TMSS method is anticipated to guide us to new synthetic protocols.

Acknowledgements

The authors gratefully acknowledge financial support from National Natural Science Foundation of China (Grant No. 21231001, 20921001, 21301180 and 21131004) and the 973 Program (2013CB933004), and the "Strategic Priority Research Program" of the Chinese Academy of Sciences (grant number XDA09020000).

Notes and references

- X. Liu, N. Fechner and M. Antonietti, *Chem. Soc. Rev.*, 2013, **42**, 8237–8265.
- W. Xiao and D. Wang, *Chem. Soc. Rev.*, 2014, **43**, 3215–3228.
- N. V. Plechkova and K. R. Seddon, *Chem. Soc. Rev.*, 2008, **37**, 123–150.
- R. E. Schaak and T. E. Mallouk, *Chem. Mater.*, 2002, **14**, 1455–1471.
- Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz and F. Lichtenberg, *Nature*, 1994, **372**, 532–534.
- Z. Pan, Q. Wang, J. Chen, C. Liu, L. Fan, L. Liu, L. Fang and X. Xing, *J. Am. Ceram. Soc.*, 2015, **98**, 104–108.
- S. F. Poterala, Y. Chang, T. Clark, R. J. Meyer and G. L. Messing, *Chem. Mater.*, 2010, **22**, 2061–2068.
- Y. Xia, P. Yang, Y. Sun, Y. Wu, B. Mayers, B. Gates, Y. Yin, F. Kim and H. Yan, *Adv. Mater.*, 2003, **15**, 353–389.
- M. G. Kanatzidis, R. Pöttgen and W. Jeitschko, *Angew. Chem., Int. Ed.*, 2005, **44**, 6996–7023.
- X. An, Y. Wang, J. Deng, J. Chen and X. Xing, *Mater. Res. Bull.*, 2014, **51**, 74–79.
- X. An, Y. Wang, J. Deng, J. Chen, R. Yu and X. Xing, *Inorg. Chem. Commun.*, 2014, **44**, 79–82.
- Z. Cai, X. Xing, R. Yu, G. Liu and Q. Xing, *J. Alloys Compd.*, 2006, **420**, 273–277.
- J. Chen, C. Zhang and X. Xing, *Mater. Lett.*, 2008, **62**, 2332–2334.
- J. Deng, J. Chen, R. Yu, G. Liu and X. Xing, *Int. J. Mater. Res.*, 2009, **100**, 1552–1556.
- J. X. Deng, L. H. Li, J. Chen, R. B. Yu and X. R. Xing, *Inorg. Chem. Commun.*, 2012, **21**, 92–95.
- L. Hu, J. Chen, L. Fan, J. Deng, R. Yu and X. Xing, *J. Am. Ceram. Soc.*, 2014, **97**, 1009–1011.
- L. H. Li, J. Chen, J. X. Deng, R. B. Yu, L. J. Qiao, G. R. Liu and X. R. Xing, *Eur. J. Inorg. Chem.*, 2008, 2186–2190.
- L. H. Li, J. X. Deng, J. Chen, R. B. Yu, L. J. Qiao and X. R. Xing, *J. Alloys Compd.*, 2009, **471**, 428–431.
- L. H. Li, X. R. Xing, J. Chen, Z. Y. Cai, J. X. Deng, C. Sun and G. R. Liu, *Chin. J. Inorg. Chem.*, 2006, **22**, 1491–1494.
- X. Xing, S. Dai, Z. Zhu and T. Tanaka, *Thermochim. Acta*, 2002, **383**, 31–35.
- X. Xing, C. Zhang, L. Qiao, G. Liu and J. Meng, *J. Am. Ceram. Soc.*, 2006, **89**, 1150–1152.
- X. Xing, Z. Zhu, S. Dai and T. Tanaka, *Thermochim. Acta*, 2001, **372**, 109–112.
- I. Pribošič, D. Makovec and M. Drogenik, *Chem. Mater.*, 2005, **17**, 2953–2958.
- C.-Y. Xu, L. Zhen, R. Yang and Z. L. Wang, *J. Am. Chem. Soc.*, 2007, **129**, 15444–15445.
- L. H. Li, J. X. Deng, J. Chen, X. Y. Sun, R. B. Yu, G. R. Liu and X. R. Xing, *Chem. Mater.*, 2009, **21**, 1207–1213.
- A. C. Santulli, H. Zhou, S. Berweger, M. B. Raschke, E. Sutter and S. S. Wong, *CrystEngComm*, 2010, **12**, 2675–2678.
- L.-Q. Cheng, K. Wang and J.-F. Li, *Chem. Commun.*, 2013, **49**, 4003–4005.
- L.-Q. Cheng, K. Wang, Q. Yu and J.-F. Li, *J. Phys. Chem. C*, 2014, **2**, 1519–1524.
- L.-Q. Cheng, K. Wang, J.-F. Li, Y. Liu and J. Li, *J. Phys. Chem. C*, 2014, **2**, 9091–9098.
- J. Boltersdorf, N. King and P. A. Maggard, *CrystEngComm*, 2015, **17**, 2225–2241.
- K.-C. Huang, T.-C. Huang and W.-F. Hsieh, *Inorg. Chem.*, 2009, **48**, 9180–9184.
- D. K. Lee, I.-S. Cho, S. Lee, D. H. Kim, H.-W. Shim, D.-W. Kim and K. S. Hong, *Eur. J. Inorg. Chem.*, 2010, 1343–1347.
- J. Dupont, R. F. de Souza and P. A. Z. Suarez, *Chem. Rev.*, 2002, **102**, 3667–3692.
- R. E. Cohen, *Nature*, 1992, **358**, 136–138.
- S.-W. Cheong and M. Mostovoy, *Nat. Mater.*, 2007, **6**, 13–20.
- Z. Cai, X. Xing, R. Yu, X. Sun and G. Liu, *Inorg. Chem.*, 2007, **46**, 7423–7427.
- M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science*, 2012, **338**, 643–647.
- D. Liu, Y. Yan and H. Zhou, *J. Am. Ceram. Soc.*, 2007, **90**, 1323–1326.
- Y. Saito and H. Takao, *Jpn. J. Appl. Phys.*, 2006, **45**, 7377–7381.



- 40 Y. Saito, H. Takao and K. Wada, *Ceram. Int.*, 2008, **34**, 745–751.
- 41 X. Yan, F. Gao and Z. Liu, *Ceram. Int.*, 2014, **40**, 4927–4932.
- 42 W. Zhao, H. Zhou, Y. Yan and D. Liu, *J. Am. Ceram. Soc.*, 2008, **91**, 1322–1325.
- 43 A. Hussain, J. U. Rahman, F. Ahmed, J.-S. Kim, M.-H. Kim, T.-K. Song and W.-J. Kim, *J. Eur. Ceram. Soc.*, 2015, **35**, 919–925.
- 44 Y. Saito, H. Takao, T. Tani, T. Nonoyama, K. Takatori, T. Homma, T. Nagaya and M. Nakamura, *Nature*, 2004, **432**, 84–87.
- 45 W. Zeng, X.-M. Tao, S. Chen, S. Shang, H. L. W. Chan and S. H. Choy, *Energy Environ. Sci.*, 2013, **6**, 2631–2638.
- 46 Y. Yan, D. Liu, W. Zhao, H. Zhou and H. Fang, *J. Am. Ceram. Soc.*, 2007, **90**, 2399–2403.
- 47 Y. Nakayama, P. J. Pauzuskie, A. Radenovic, R. M. Onorato, R. J. Saykally, J. Liphardt and P. Yang, *Nature*, 2007, **447**, 1098–1101.
- 48 Z. L. Wang and J. H. Song, *Science*, 2006, **312**, 242–246.
- 49 Y. Saito and H. Takao, *J. Eur. Ceram. Soc.*, 2007, **27**, 4085–4092.
- 50 F. Caruso, R. A. Caruso and H. Möhwald, *Science*, 1998, **282**, 1111–1114.
- 51 L. H. Li, J. X. Deng, R. B. Yu, J. Chen, X. W. Wang and X. R. Xing, *Inorg. Chem.*, 2010, **49**, 1397–1403.
- 52 D. P. Chen, W. Bowers and S. E. Skrabalak, *Chem. Mater.*, 2015, **27**, 174–180.
- 53 N. S. P. Bhuvanesh and P. M. Woodward, *J. Am. Chem. Soc.*, 2002, **124**, 14294–14295.
- 54 D. Arney and P. A. Maggard, *ACS Catal.*, 2012, **2**, 1711–1717.
- 55 J. Boltersdorf and P. A. Maggard, *ACS Catal.*, 2013, **3**, 2547–2555.
- 56 S. F. Poterala, J. R. J. Meyer and G. L. Messing, *J. Am. Ceram. Soc.*, 2011, **94**, 2323–2329.
- 57 L. H. Li, J. X. Deng, R. B. Yu, J. Chen, Z. Wang and X. R. Xing, *J. Mater. Chem. A*, 2013, **1**, 11894–11900.
- 58 P. X. Gao, J. Song, J. Liu and Z. L. Wang, *Adv. Mater.*, 2007, **19**, 67–72.
- 59 Y. Wang, S. Xie, J. Deng, S. Deng, H. Wang, H. Yan and H. Dai, *ACS Appl. Mater. Interfaces*, 2014, **6**, 17394–17401.
- 60 R. E. Schaak and T. E. Mallouk, *J. Am. Chem. Soc.*, 2000, **122**, 2798–2803.
- 61 T. Gao, J. Liao, J. Wang, Y. Qiu, Q. Yang, M. Zhang, Y. Zhao, L. Qin, H. Xue, Z. Xiong, L. Chen and Q.-M. Wang, *J. Phys. Chem. A*, 2015, **3**, 9965–9971.
- 62 M.-A. Einarsrud and T. Grande, *Chem. Soc. Rev.*, 2014, **43**, 2187–2199.
- 63 A. Magrez, E. Vasco, J. W. Seo, C. Dieker, N. Setter and L. Forró, *J. Phys. Chem. B*, 2006, **110**, 58–61.
- 64 J. N. Coleman, M. Lotya, A. O'Neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, I. V. Shvets, S. K. Arora, G. Stanton, H.-Y. Kim, K. Lee, G. T. Kim, G. S. Duesberg, T. Hallam, J. J. Boland, J. J. Wang, J. F. Donegan, J. C. Grunlan, G. Moriarty, A. Shmeliov, R. J. Nicholls, J. M. Perkins, E. M. Grievson, K. Theuwissen, D. W. McComb, P. D. Nellist and V. Nicolosi, *Science*, 2011, **331**, 568–571.
- 65 D. Lv, R. Zuo and S. Su, *J. Am. Ceram. Soc.*, 2012, **95**, 1838–1842.
- 66 T. A. Schaedler, A. J. Jacobsen, A. Torrents, A. E. Sorensen, J. Lian, J. R. Greer, L. Valdevit and W. B. Carter, *Science*, 2011, **334**, 962–965.
- 67 W. F. Libby, *Science*, 1971, **171**, 499–500.
- 68 J. Zhu, H. Li, L. Zhong, P. Xiao, X. Xu, X. Yang, Z. Zhao and J. Li, *ACS Catal.*, 2014, **4**, 2917–2940.
- 69 J. Zhang, Z. Pan, F.-F. Guo, W.-C. Liu, H. Ning, Y. B. Chen, M.-H. Lu, B. Yang, J. Chen, S.-T. Zhang, X. Xing, J. Rödel, W. Cao and Y.-F. Chen, *Nat. Commun.*, 2015, **6**, 6615.
- 70 Z. L. Wang and J. Song, *Science*, 2006, **312**, 242–246.
- 71 J. H. Jung, M. Lee, J.-I. Hong, Y. Ding, C.-Y. Chen, L.-J. Chou and Z. L. Wang, *ACS Nano*, 2011, **5**, 10041–10046.
- 72 C. K. Jeong, K.-I. Park, J. Ryu, G.-T. Hwang and K. J. Lee, *Adv. Funct. Mater.*, 2014, **24**, 2620–2629.
- 73 P. Muralt, R. G. Polcawich and S. Trolrier-McKinstry, *MRS Bull.*, 2009, **34**, 658–664.
- 74 W. Wu, X. Wen and Z. L. Wang, *Science*, 2013, **340**, 952–957.
- 75 W. Wu, L. Wang, Y. Li, F. Zhang, L. Lin, S. Niu, D. Chenet, X. Zhang, Y. Hao, T. F. Heinz, J. Hone and Z. L. Wang, *Nature*, 2014, **514**, 470–474.
- 76 H. Kang, J. Chen, L. Liu, C. Hu, L. Fang and X. Xing, *Inorg. Chem. Commun.*, 2013, **31**, 66–68.
- 77 K.-I. Park, J. H. Son, G.-T. Hwang, C. K. Jeong, J. Ryu, M. Koo, I. Choi, S. H. Lee, M. Byun, Z. L. Wang and K. J. Lee, *Adv. Mater.*, 2014, **26**, 2514–2520.
- 78 S.-T. Zhang, A. B. Kouniga, E. Aulbach, H. Ehrenberg and J. Roedel, *Appl. Phys. Lett.*, 2007, **91**, 112906.
- 79 X. An, J. Deng, J. Chen and X. Xing, *Mater. Res. Bull.*, 2013, **48**, 4984–4988.
- 80 K. Domen, J. Yoshimura, T. Sekine, A. Tanaka and T. Onishi, *Catal. Lett.*, 1990, **4**, 339–343.
- 81 D. Arney, B. Porter, B. Greve and P. A. Maggard, *J. Photochem. Photobiol., A*, 2008, **199**, 230–235.
- 82 D. Arney, C. Hardy, B. Greve and P. A. Maggard, *J. Photochem. Photobiol., A*, 2010, **214**, 54–60.
- 83 W. Zhang, J. Chen, X. An, Q. Wang, L. Fan, F. Wang, J. Deng, R. Yu and X. Xing, *Dalton Trans.*, 2014, **43**, 9255–9259.
- 84 J. Chen, L. Hu, J. Deng and X. Xing, *Chem. Soc. Rev.*, 2015, **44**, 3522–3567.
- 85 W. Eerenstein, N. D. Mathur and J. F. Scott, *Nature*, 2006, **442**, 759–765.
- 86 J. Wang, J. B. Neaton, H. Zheng, V. Nagarajan, S. B. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D. G. Schlom, U. V. Waghmare, N. A. Spaldin, K. M. Rabe, M. Wuttig and R. Ramesh, *Science*, 2003, **299**, 1719–1722.
- 87 I. Grinberg, D. V. West, M. Torres, G. Gou, D. M. Stein, L. Wu, G. Chen, E. M. Gallo, A. R. Akbashev, P. K. Davies, J. E. Spanier and A. M. Rappe, *Nature*, 2013, **503**, 509–512.
- 88 M. Fiebig, T. Lottermoser, D. Frohlich, A. V. Goltsev and R. V. Pisarev, *Nature*, 2002, **419**, 818–820.
- 89 J. Chen, X. Xing, A. Watson, W. Wang, R. Yu, J. Deng, L. Yan, C. Sun and X. Chen, *Chem. Mater.*, 2007, **19**, 3598–3600.
- 90 G. Xu, H. Bai, X. Huang, W. He, L. Li, G. Shen and G. Han, *J. Phys. Chem. A*, 2015, **3**, 547–554.



- 91 Y. Mao, J. Parsons and J. S. McCloy, *Nanoscale*, 2013, 5, 4720–4728.
- 92 J. Chen, R. Yu, L. Li, C. Sun, T. Zhang, H. Chen and X. Xing, *Eur. J. Inorg. Chem.*, 2008, 3655–3660.
- 93 M. Dion, M. Ganne and M. Tournoux, *Mater. Res. Bull.*, 1981, 16, 1429–1435.
- 94 M. M. J. Treacy, S. B. Rice, A. J. Jacobson and J. T. Lewandowski, *Chem. Mater.*, 1990, 2, 279–286.
- 95 A. J. Jacobson, J. W. Johnson and J. T. Lewandowski, *Inorg. Chem.*, 1985, 24, 3727–3729.
- 96 F. Meng, Z. Hong, J. Arndt, M. Li, M. Zhi, F. Yang and N. Wu, *Nano Res.*, 2012, 5, 213–221.
- 97 X. He, J. Wang, R. Kloepsch, S. Krueger, H. Jia, H. Liu, B. Vortmann and J. Li, *Nano Res.*, 2014, 7, 110–118.

