



Cite this: *Phys. Chem. Chem. Phys.*,
2017, 19, 23704

The relevance of structural features of cellulose and its interactions to dissolution, regeneration, gelation and plasticization phenomena

Björn Lindman,^{ab} Bruno Medronho,^{ib} *^c Luis Alves,^d Carolina Costa,^a
Håkan Edlund^{ib}^a and Magnus Norgren^a

Cellulose is the most abundant polymer and a very important renewable resource. Since cellulose cannot be shaped by melting, a major route for its use for novel materials, new chemical compounds and renewable energy must go via the solution state. Investigations during several decades have led to the identification of several solvents of notably different character. The mechanisms of dissolution in terms of intermolecular interactions have been discussed from early work but, even on fundamental aspects, conflicting and opposite views appear. In view of this, strategies for developing new solvent systems for various applications have remained obscure. There is for example a strong need for using forest products for higher value materials and for environmental and cost reasons to use water-based solvents. Several new water-based solvents have been developed recently but there is no consensus regarding the underlying mechanisms. Here we wish to address the most important mechanisms described in the literature and confront them with experimental observations. A broadened view is helpful for improving the current picture and thus cellulose derivatives and phenomena such as fiber dissolution, swelling, regeneration, plasticization and dispersion are considered. In addition to the matter of hydrogen bonding *versus* hydrophobic interactions, the role of ionization as well as some applications of new knowledge gained are highlighted.

Received 13th April 2017,
Accepted 22nd May 2017

DOI: 10.1039/c7cp02409f

rsc.li/pccp

Introduction

Physico-chemical studies of cellulose and its intermolecular interactions obviously have a long history. In early work in developing the concept of polymers, cellulose played a central role and was a natural early study object by Staudinger, Svedberg and other pioneers in the field of macromolecules. The ultra-centrifuge developed by Svedberg gave direct proof of the existence of high molecular weight molecules. This proof would have been more difficult to obtain if Svedberg had started his work with a highly polydisperse compound like cellulose and not (partly by chance) a high molecular weight protein. Cellulose early on became an important study object among polymer physical chemists and Svedberg would return to such studies.^{1,2} A central part of these and other attempts to characterize cellulose molecules was obviously to dissolve cellulose, and several solvents,

more or less exotic, were developed, *inter alia* for molecular weight determination.³ In this early period, researchers typically investigated different macromolecules in parallel and comparing solubility characteristics of different polymers was helpful for understanding the intermolecular interactions involved.

Research on polymers has clearly grown enormously and has become very specialized. Currently cellulose work is very extensive and includes large efforts to develop new solvent systems. Earlier widespread studies regarding swelling phenomena and structural changes in cellulose due to sodium hydroxide were originated after Mercer's discovery (so-called mercerization process) in 1844. It was found that cellulose shows a maximum swelling in aqueous alkali solutions in a specific concentration range, namely 8–10 wt% aqueous sodium hydroxide and 5–10 wt% aqueous lithium hydroxide, at a relatively low temperature.^{4–9} These in-depth studies on cellulose swelling opened the door to cellulose dissolution in 8–10 wt% aqueous sodium hydroxide and in 6 wt% aqueous lithium hydroxide solution at 4 °C.¹⁰

Since then, important progress has been made, for example, by Lina Zhang and coworkers in Wuhan, who elaborated additives like urea and thiourea as important facilitators of dissolution.^{11–16}

Lithium salts are also worth mentioning due to their relevance for the analysis of cellulose and preparation of a wide variety of

^a FSCN, Mid Sweden University, SE-851 70 Sundsvall, Sweden

^b Physical Chemistry, University of Lund, P.O. Box 124, S-221 00 Lund, Sweden

^c Faculty of Sciences and Technology (MeditBio), Ed. 8, University of Algarve, Campus de Gambelas, 8005-139 Faro, Portugal. E-mail: bfmedronho@ualg.pt

^d CQC, University of Coimbra, Department of Chemistry, 3004-535 Coimbra, Portugal



derivatives. In this respect, the DMAc/LiCl mixture, developed by McCormick, should be highlighted.¹⁷ *N*-Oxides of tertiary amines, in particular *N*-methylmorpholine-*N*-oxide (NMO),^{18,19} emerged as the best of the amine-oxides in the late 1970s; solutions up to 23 wt% of cellulose can be obtained by dissolving the polymer in NMO/water mixtures, and subsequently removing water under vacuum.^{20–22} This constitutes the basis of the Lyocell process whose commercial potential has been demonstrated and is now applied on a large scale.²³

Regarding interactions that limit cellulose solubility in water and are responsible for cellulose aggregation, much focus has been on hydrogen bonds. This is in striking contrast to discussions about interactions of other polysaccharide systems.

Purpose

A few years ago, in approaches from Swedish industry, we were asked to analyse the present state of cellulose solvents and hopefully suggest new routes. A general outcome of the survey of recent literature²⁴ was that the insolubility in water was attributed to strong cellulose–cellulose hydrogen bonds, a view in conflict with our general understanding of water as a solvent. Instead it was argued that cellulose is markedly amphiphilic and that the aqueous insolubility could be mainly attributed to hydrophobic interactions.^{24,25}

It is well known that cellulose solubility in water increases strongly at extreme pH values, again interpreted in the current literature in terms of breaking of hydrogen bonds. We argued instead that this is a typical polyelectrolyte behaviour related to a protonation/deprotonation process giving cellulose molecules a net charge. Our analysis, published in a Festschrift for a colleague,²⁴ led to an invitation for the opening lecture of the ZELLCHEMING conference in Wiesbaden, Germany (June 28–30, 2011). On the basis of this, Wolfgang Glasser, editor of *Cellulose*, invited a paper.²⁵ In order to stimulate discussion he invited a number of leading researchers in the field to critically examine our views.²⁶ Unsurprisingly it was found that our views were far from novel or original but that similar findings could be seen in earlier publications.^{27–30} However, such contributions had essentially drowned in a flood of publications identifying hydrogen bonding as the main reason for the insolubility of cellulose in water.

During the years since these publications the activity regarding cellulose dissolution has become even more intense and several new studies have been published. This gives an excellent opportunity to return to basic aspects and shed further light on the problem.

Hydrogen bonding vs. hydrophobic interactions

Considering the general features of dissolution of a solid in a liquid we note that the process is a delicate balance between entropy, favoring solubility, and energy or interactions typically opposing solubility. Depending on the interactions mainly in the solid state, the latter can be a weak or strong force. On dissolution

we have to break intermolecular interactions in the solute, like the hydrogen bonds between cellulose molecules, which are unfavorable for dissolution. However, on dissolution we establish new interactions between the solute and the solvent molecules and it is the balance of different interactions that will determine the outcome. For the case of cellulose in water it is noted that we have to consider hydrogen bonds not only between cellulose molecules but also between cellulose and water and between water molecules. It appears that they are not significantly different and therefore aqueous insolubility cannot be attributed to hydrogen bonding. A detailed analysis of the balance of interactions by Bergenstr hle *et al.* clearly demonstrated the same point as has also other analyses.^{31–33}

There are several observations that suggest that hydrophobic interactions are decisive for the behavior of cellulose in aqueous systems:³⁴

- In the structure of cellulose there is a clear segregation into polar (OH) and nonpolar (CH) patches, and thus a clear amphiphilicity.^{35–38} Due to the hydrophobic properties of the glucopyranose plane, the cellulose chains can stack *via* hydrophobic interactions and can form a sheet-like structure (Fig. 1). This was already recognized by Sponser's diffraction work³⁹ and later by Warwicker and Wright.⁴⁰

- Urea (as well as thiourea and some other cosolutes) facilitates cellulose dissolution. This correlates well with the effect of urea on hydrophobic interactions as seen for example for proteins (denaturation by urea) and surfactant micelles (demicellization by urea).^{41–44}

- After dissolution of native cellulose (cellulose I), which is metastable, one typically observes gelation, which is due to cellulose aggregation and the onset of precipitation of (stable) cellulose II.^{45,46} The fact that gelation is significantly reduced in the presence of surfactants points to the presence of hydrophobic parts.³⁴

- Solutions of organic acids or bases are much better solvents than those of inorganic ones. Furthermore, there are



Fig. 1 Cellulose II crystal and the models of molecular sheets: (A) hydrogen bonded (HB) molecular sheet; (B) van der Waals-associated (VW) molecular sheet. (Reprinted from ref. 38: H. Miyamoto, M. Umemura, T. Aoyagi, C. Yamane, K. Ueda and K. Takahashi, Structural reorganization of molecular sheets derived from cellulose II by molecular dynamics simulations, *Carbohydr. Res.*, 2009, **344**(9), 1085–1094. Copyright 2009, with permission from Elsevier.)



Klemm: "The amphiphilic nature of cellulose and its interpretation as well as the comparison with the amphiphilic

oligoglucans of the cyclodextrin type have been under discussion for a long time.”

Atalla: “The hypothesis of Lindman serves the field well in reopening questions regarding the stability of cellulose in aqueous media. It discusses some but by no means all of the phenomena and issues that are relevant to understanding the solubility of cellulose or the lack thereof. But the conclusion attributing the lack of solubility in water to a strong contribution by its amphiphilicity is as simplistic as its prior attribution to hydrogen bonding.”

Burchard: “No doubt, the anhydro-glucose unit (AGU) has noticeable hydrophobicity. This is evidenced by the inclusion complexes of hydrocarbons that are observed with cyclodextrin and one of the amylose helices. This behaviour could not be estimated from the outset on the basis of the chemical structure of the anhydro-glucose unit alone. Clearly, the ring skeleton is hydrophobic and contains only one polar oxygen unit. The symmetry is perturbed by the primary OH group sticking out at C6 position, which is hydrophilic.”

Glasser: “In summary, the Lindman hypothesis seems to agree with the general perspective (as expressed by the debaters) of cellulose as a polymer in which intermolecular stress transfer involves more than hydrogen bonds. Hydrophobic and amphiphilic behaviors have been acknowledged for some time but may have been under-estimated in conventional considerations of structure, solubility, *etc.*” “It is apparent from these studies that van der Waals attractive forces and hydrophobic interactions may prevail not only in the formation of crystalline cellulose morphologies but also in the formation of a cellulose-to-lignin interface. . .”

Does cellulose ionization contribute to solubility in water?

There has been, during the last decade and more, a huge renewed interest in cellulose dissolution in alkaline solutions (see, for instance, ref. 80 and references therein). In the very large number of publications on the topic there is rarely a discussion in terms of ionization of cellulose. Rather dissolution is frequently attributed to the hydroxide ions “attacking” the hydrogen bonds. It is unclear if this is a kinetic or thermodynamic argument and what this implies for the mechanism of cellulose self-association as pH is lowered. Dissolution in aqueous alkali has also been discussed in terms of special sodium hydroxide hydrates.^{81,82} Special attention has also been paid to the difference between different alkali ions. This alkali ion specificity has been attributed to specific ion binding effects. A rather strong input to this hydrate hypothesis has come from Zhang's group where the NaOH or LiOH hydrates (even when urea is present) are said to destroy the inter- and intra-hydrogen bonds between cellulose molecules while the urea hydrates are believed to work as donors and receptors of hydrogen bonds between solvent molecules, thus preventing cellulose aggregation and leading to molecular dissolution of cellulose.^{13–15,83–87}

Solubility and miscibility are, in almost all cases, due to entropy of mixing and cellulose should not constitute an

exception.⁵⁹ The solubility of a polymer is generally low because of a low translational entropy. For a stiff polymer it is even lower because of a low configurational entropy. If the polymer is ionized and becomes a polyelectrolyte the situation is quite different, mainly because of the large entropy contribution from the counterions; Coulombic interactions may also contribute but are generally much weaker.^{88,89} Therefore, polymers that ionize are generally soluble in water, even if they are not very polar. The counterion entropy effect is reduced or lost if an electrolyte is added and in line with this many polyelectrolytes lose their solubility on addition of salt.

It is striking that whereas this polyelectrolyte view (also important in fiber swelling, *cf.* below) is clearly understood in the earlier literature⁹⁰ this perspective is lost in some recent literature. In two recent reviews,^{80,91} OH deprotonation is hardly mentioned in connection to alkali systems. Instead, the effect of alkali is discussed in terms of weakening of hydrogen bonds between cellulose chains and specific ion interactions. As mentioned above, the dissolution of cellulose under alkaline conditions is thus sometimes attributed to hydroxide ions attacking the hydrogen bonds between cellulose molecules. We can compare this with our picture of the pH dependent solubility of two near-lying comparisons, sodium carboxymethyl cellulose (CMC) and chitosan. As the pH value decreases, CMC will be protonated. CMC will gradually change from the salt type into the water-insoluble acid type and precipitate from the solution. We can dissolve the precipitate by adding NaOH and increase the pH, very similar to what happens with cellulose at high pH. In the case of CMC we would not describe the effect in terms of OH[−] ions (at 10^{−10} molar) attacking hydrogen bonds. Likewise with chitosan, it is water-soluble at low but not at high pH. Again we ascribe this to protonation and ionization rather than H⁺ ions attacking intermolecular hydrogen bonds.

As indicated, early literature ascribed cellulose solubility at extreme pH values to protonation/deprotonation effects leading to charging up. However, this picture was later lost in most literature partly since it was difficult to directly demonstrate ionization effects in experiments. One exception worth mentioning is the ¹H and ¹³C NMR work of Isogai where low molecular weight cellulose (DP = 15) was investigated in 4–30 wt% NaOD/D₂O solvent mixtures.⁹² From the relationship between the ¹H- and ¹³C-chemical shifts of the cellulose and NaOD concentrations it was possible to infer on the dissociation state of three hydroxyl groups of cellulose in aqueous NaOH solutions. It is further stated that “although alcoholic hydroxyl groups may not form stable alcoholates, *i.e.* completely dissociated forms, in aqueous alkaline environment, they may be able to form some sort of dissociated structures of relatively short duration even in aqueous alkaline solutions”. Later studies by Alves *et al.* gave strong qualitative support to the work of Isogai in two ways, namely by demonstrating large pH dependencies of NMR chemical shifts and by nonspecific electrolyte effects in decreasing cellulose solubility.^{93–95} With self-diffusion NMR, Gentile and Olsson have shown in a strong alkaline solvent that the tetrabutylammonium cation (TBA⁺) binds to cellulose with approximately 1.2 TBA⁺ ions per glucose unit and the reason for such binding is suggested to be



the electrostatic interaction with the deprotonated hydroxyl groups on cellulose combined with hydrophobic interactions.⁹⁶ For cellulose dissolution in an aqueous metal complex based system, it has been realized that the deprotonation of OH-groups (C2 and C3) is necessary before the complex can be established at those positions.^{97–100}

Recently, more conclusive evidence for ionization at high pH has been obtained by Bialik *et al.* in studies on model systems.¹⁰¹ To elucidate the dissolution mechanism, these authors performed electrophoretic NMR on cellobiose, a subunit of cellulose, showing that cellobiose acts as an acid with two dissociation steps at pH 12 and 13.5 (Fig. 2, left). Chemical shift differences between cellobiose in NaOH and NaCl were estimated using 2D NMR and compared to theoretical shift differences upon deprotonation. The dissociation steps are the deprotonation of the hemiacetal OH group and the deprotonation of one of four OH groups on the non-reducing anhydroglucose unit. Molecular dynamics simulations revealed that aggregation is suppressed upon charging cellulose chains in solution (Fig. 2, right).

These findings strongly suggest that cellulose is to a large extent charged in concentrated aqueous alkali, clearly a crucial factor for dissolution. We believe that this insight, largely overlooked in the current literature, is important for understanding cellulose dissolution.

As mentioned, a number of reports in the literature have found cation-specific effects in dissolution by alkali hydroxides, for example NaOH being more efficient than KOH. However, Bialik *et al.* found that ionization does not depend on whether NaOH or KOH is used to obtain a particular pH.¹⁰¹ A larger amount of KOH is, however, needed to obtain the same pH because NaOH is a stronger base. Hence, the apparent cation specificity previously reported^{102,103} may appear due to the interaction between alkali and OH[−] ions. Thus there is no support for the notion that different interactions between different alkali ions and cellulose play a role. Further studies like the one of Bialik *et al.* are needed to throw light on the generality of charging up of cellulose as an important mechanism for dissolution. For example, Bialik *et al.* showed that because of

selective association there is the formation of charged cellulose species in ionic liquids.¹⁰⁴

What can we learn from cellulose derivatives?

Recent research on cellulose is frequently not performed with reference to studies of other polysaccharides, not even cellulose derivatives (A notable exception is EPNOE, the European Polysaccharide Network of Excellence, directed by P. Navard.).¹⁰⁵ In our opinion important insight into mechanisms can be gained from such a broader scope.

A large number of cellulose derivatives have been prepared for a long time, and have many important applications. They have also been the subject of extensive research. Many of them are water-soluble, so their interactions can be easily investigated. The most studied are methyl cellulose (MC), hydroxyethyl cellulose (HEC), ethylhydroxyethyl cellulose (EHEC), hydroxypropyl cellulose (HPC), CMC, and cationic HECs (catHEC). The cellulose derivatives can be ionic or nonionic and have different polarities, higher or lower than cellulose itself, and higher or lower hydrogen bonding capacity. Since cellulose derivatives retain important features of the cellulose molecule and are easily dissolved in the molecular state, their study can shed important light on the properties of molecular cellulose. One common feature of the nonionic cellulose derivatives and cellulose is the anomalous temperature dependence of solubility, *i.e.* that solubility in water increases at lower temperature. Solubility of nonionic cellulose derivatives is strongly affected by cosolutes (see, for example, ref. 106). For electrolytes, different anions have strong effects; large anions like I[−] or SCN[−] increase the solubility considerably whereas Cl[−] and SO₄^{2−} decrease it. This can be attributed to a weak association for the former ones and depletion for the latter ones.⁷⁹

A common aspect of surfactants in water is the strong tendency to associate to macroscopic or molecular hydrophobic sites; this is illustrated by the non-cooperative adsorption to hydrophobic surfaces and by the binding to cosolutes with hydrophobic groups. Mixed solutions of different surfactants and a range of cellulose derivatives have been extensively investigated.^{107–110} A very general feature is an association, as can be inferred from solubility as well as from direct binding isotherms. Notably, binding is observed even if the substitution is such that the cellulose derivatives are more polar than cellulose itself. This gives a strong indication that cellulose molecules have significant hydrophobic properties.

We will illustrate the delicate balance between electrostatic and hydrophobic interactions by two very different cases, a cationic hydroxyethyl cellulose derivative (catHEC) and a non-ionic cellulose ether, ethyl hydroxyethyl cellulose (EHEC). In both cases we consider a common surfactant, sodium dodecyl sulfate (SDS). The surfactant binding isotherm for catHEC illustrated in Fig. 3 shows that binding occurs in two distinct steps, which can be attributed to two driving forces, electrostatic and hydrophobic.¹¹¹ In a first binding step the oppositely


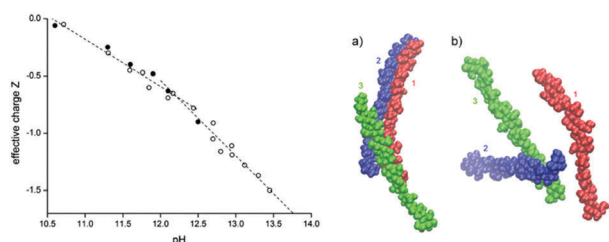


Fig. 2 (left) Effective charge, Z , of cellobiose as a function of the solution pH adjusted by adding either KOH (closed circles) or NaOH (open circles). The estimated experimental uncertainty of Z is ± 0.1 . Dashed lines are linear fits to data below and above pH = 12.1, respectively. (right) Cellulose configurations in the last frame of a 1 μ s simulation for (a) neutral and (b) deprotonated. (Adapted with permission from ref. 101: E. Bialik, B. Stenqvist, Y. Fang, Å. Östlund, I. Furo, B. Lindman, M. Lund and D. Bernin, Ionization of Cellobiose in Aqueous Alkali and the Mechanism of Cellulose Dissolution, *J. Phys. Chem. Lett.*, 2016, **7**(24), 5044–5048. Copyright 2016, American Chemical Society.)



Another indication of the inherent amphiphilicity of the cellulose molecule can be seen in the adsorption properties of cellulose derivatives. Nonionic polymers have in general a large tendency to adsorb on different surfaces as a result of the low translational entropy. For cellulose derivatives there is a striking difference between polar and nonpolar surfaces as illustrated in Fig. 6.¹⁰⁶ The larger tendency for adsorption to nonpolar surfaces indicates the role of hydrophobic interactions. Adsorption studies

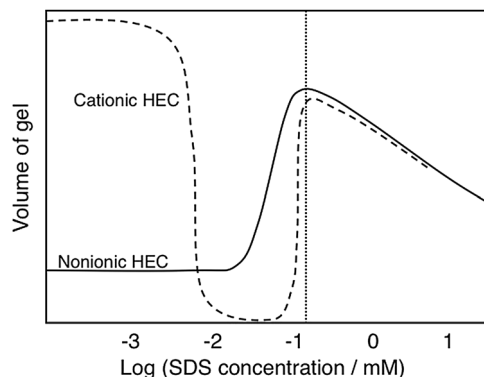

These and several other studies of cellulose derivatives point to the strong effect of hydrophobic interactions in aqueous solution. On the other hand, there is no indication of hydrogen-bonding driving association between the polymer molecules in water or playing a role in association phenomena in general. For example, we see no correlation between association and hydrogen bonding capacity. Cellulose derivatives typically have a somewhat patchy substitution pattern and it has been observed that unsubstituted parts of cellulose molecules can associate into long-lived pseudo-crystalline aggregates which locally have a structure very much resembling that in cellulose itself.¹¹⁴ This association due to “microcrystallites” is strongly

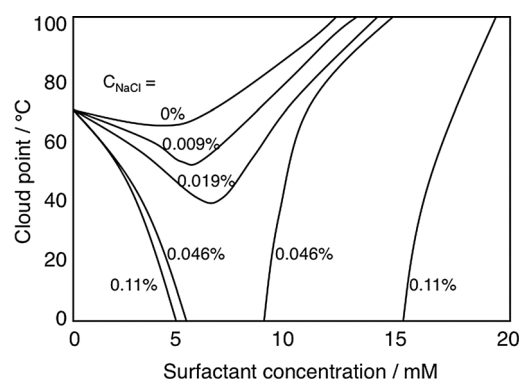




Fig. 6 The adsorption of EHEC from dilute solutions is distinctly different for polar (silica) and nonpolar (hydrophobized silica) surfaces. (Reprinted from ref. 106: M. Malmsten and B. Lindman, Ellipsometry studies of the adsorption of cellulose ethers, *Langmuir*, 1990, **6**, 357–364. Copyright 1990, American Chemical Society.)

dependent on the distribution of substituents along the cellulose molecules and is promoted by “blockiness”. The presence of crystallinity was indicated by X-ray diffraction for concentrated solutions giving similar packing as for native cellulose. The observed gelation in such solutions induced by ionic surfactants is governed by an interplay between swelling (caused by the surfactant charges) and connectivity (due to hydrophobic association).¹¹⁵ Gelation in mixtures of surfactants and typical hydrophobically modified polymers is caused by short-lived hydrophobic associations. However, in the work on cellulose derivatives very long-lived aggregates can be observed in NMR studies.¹¹⁶ The presence of long-lived aggregates was confirmed in investigations using surface force apparatus, static light scattering and flow field fractionation chromatography.^{117,118} In conclusion this work points to a hydrophobic association mechanism distinct from the short-lived and weak one of hydrophobically modified water-soluble polymers. Rather association was found to be related to unsubstituted parts of the cellulose derivatives forming microscopic pseudo-crystalline regions. This is supported by the wide-angle X-ray diffraction results mentioned above.

Cellulose derivatives display clearly the delicate balance between hydrophobic and electrostatic interactions as we have seen throughout for cellulose itself.

Not only thermodynamics

The dissolution of any polymer is a slow process and equilibrium in polymer systems may not be reached under practical conditions. Cellulose is certainly no exception to this, rather the complex hierarchical structure of wood imposes strong kinetic barriers for any process. The fact that cellulose I, which is metastable with respect to cellulose II, can exist for 100s of years illustrates this. Another aspect of the kinetics concerns the numerous complex pretreatments of cellulose prior to dissolution, which have been described. In this treatise we have left kinetic

aspects aside and focussed on thermodynamics and intermolecular interactions.

Cellulose regeneration and gelation

Cellulose regeneration is an indispensable step for cellulose shaping and process of novel materials.^{119–121} Typically, regeneration involves the use of non-solvents, which, upon contact with the dissolved cellulose dope, induce the precipitation (coagulation) of cellulose. The kinetics of coagulation are essentially controlled by the relative diffusion velocities of solvent from the cellulose dope to the coagulation medium and the counterpart reverse process, diffusion of the non-solvent into the cellulose dope.¹²² Additionally, the type of solvent and non-solvent strongly influences the properties (morphological and mechanical) of the regenerated cellulose material.^{123,124} From a mechanistic point of view, this exchange of solvent with non-solvent is generally believed to lead to the reformation of intra- and inter-hydrogen bonds previously broken during dissolution. Water assumes a relevant role, particularly when ionic liquids (ILs) are used as cellulose solvents. For example, computational studies on the 1-ethyl-3-methylimidazolium acetate, [C2mim][Ac], and 1-butyl-3-methylimidazolium acetate, [C4mim][Ac], systems propose that the H-bonds formed between the –OH groups of cellulose and [Ac] anions diminish when adding water (works as a non-solvent). It is suggested that water forms preferentially H-bonds with the [Ac] anion and consequently, the H-bonds between cellulose molecules are reestablished, leading to precipitation.^{125–127}

The regeneration mechanism for alkali systems suggests that the inclusion complex associated with cellulose, NaOH, and, in some cases, urea or thiourea hydrates, is disrupted by adding a non-solvent such as water, leading to the self-association of cellulose. The regenerated cellulose is said to be formed through a rearrangement of the hydrogen bonds.^{128,129} Therefore, regeneration is generally assumed to be driven by H-bonding reformation.

Recent theoretical work has highlighted other interactions. For instance, the MD simulations performed by Miyamoto *et al.* suggest that the initial structure obtained during coagulation of a dope is a molecular cellulose sheet formed *via* van der Waals associations,³⁸ and that such sheets play a critical role in the final structure, *e.g.*, the crystallinity of cellulose.¹³⁰ This work supports the hypothesis of Hayashi¹³¹ and Hermans¹³² in which molecular sheet-like structures (also called plane lattice structures) have been identified as basic features of regenerated cellulose. The first experimental proof that molecular sheets are formed by hydrophobic interactions as the initial structure was demonstrated by Isobe *et al.*, who reported that the peak of the (110) plane of Na-cellulose IV first appeared when cellulose from cellulose/aqueous alkali/urea solution was regenerated.¹²³ It should be mentioned that these features were already deduced from cellulose biosynthesis where the fundamental groundwork supports the previous ideas.^{30,133,134} Essentially, it was found that cellulose crystallization is a three step process: (a) formation of monomolecular glucan chain sheets by van der



Waals forces; (b) association of these sheets into mini-crystals by H-bonding; and (c) convergence of the mini-crystals (= subelementary fibrils) into the native crystalline microfibril.

Another important issue is gelation, which can be regarded as an intermediate step in cellulose regeneration. Gelation can be triggered by changes in the solvent composition, ionic strength, pH or even temperature (the use of a non-solvent may affect various parameters at the same time). The general inability of the solvents to molecularly disperse cellulose chains leads to the formation of aggregates of cellulose chains in solution, and a fringed micelle model has been proposed to reflect the semi-crystalline structure of the native cellulose fibers.^{135,136} Gelation is said to be a consequence of the formation of a cross-linked network between the different nuclei (*i.e.* fringed micelles).¹³⁷ Recently it has been suggested that the reason for cellulose gelation may also be related to crystal polymorphism; while natural (wood) cellulose, so called cellulose I, dissolves, solutions may become supersaturated with respect to the more stable cellulose II.^{45,46} This kind of cellulose recrystallization from semi-dilute solutions may lead to gelation as chains can participate in more than one nucleus.

Surface polarity of cellulose and wettability

As mentioned above, there is a clear segregation into polar (OH) and nonpolar (CH) patches in the cellulose structure. This structural anisotropy is reflected in different properties presented by cellulose molecules such as wetting.¹³⁸ Yamane *et al.* suggested that the contact angle formed by a water droplet on regenerated cellulose films (as an index of wettability) is positively correlated with the orientation of (1–10) crystal planes and crystallinity. The hydroxyl groups of cellulose are located at the equatorial positions of glucopyranose rings, corresponding to the crystal plane (1–10), and the hydrophilicity of this surface is expected to be very high. It is also predictable that a higher planar orientation of the (1–10) planes and higher crystallinity would lead to higher density of hydroxyl groups on the surface of regenerated cellulose films, resulting in higher wettability. Regenerated cellulose films are known to be among the most hydrophilic polymeric films; the contact angle of a water droplet on typical regenerated cellulose films, such as cellophane or cuprophane, is *ca.* 12°, far lower than that of other widely used polymers. However, higher contact angles are observed in the case of amorphous regenerated cellulose samples. In the same direction, Whang *et al.* attributed the higher contact angles obtained on rayon fibers, when compared with cotton, to the significantly higher molecular orientation in cotton fibers.¹³⁹ The use of less polar coagulation media, such as ethanol, results in less crystalline materials.¹⁴⁰ Therefore, it is possible to change the wetting properties of regenerated cellulose by choosing appropriate coagulants or tuning the coagulation conditions. This has been suggested, for instance, by Badjik *et al.*, who reported differences in the wetting properties for hydroxypropyl cellulose films formed in ethanol and water.

These differences were suggested to be driven by differences in the polarity of the coagulant which induced different molecular arrangements of the hydroxypropyl cellulose molecules.¹⁴¹

Miyamoto *et al.* have used molecular dynamics (MD) simulations to investigate structural reorganization of two different kinds of molecular sheets derived from the cellulose II crystal. The authors found that the van der Waals-associated molecular sheet becomes stable in an aqueous environment with its hydrophobic moieties inside and hydrophilic moieties in the periphery. In contrast to this, a benzene environment preferred a hydrogen-bonded molecular sheet, which is expected to be the initial structure formed in benzene.³⁸ This strongly suggests that cellulose with complementary properties, *i.e.*, hydrophobic surface, can be created by structural controls such as reversing the planar orientation from (1–10) to (110) by controlling dissolution and the coagulation conditions. Additionally it was found that post-treatments with nonpolar solvents (*e.g.*, hexane), liquid ammonia or hot glycerol can, to some extent, control the wettability of the regenerated cellulose films. The hydrogen atoms are located at the axial positions of the glucopyranose rings, corresponding to the surface of (110) planes. Thus, the (110) surface is expected to be hydrophobic, and the surface energy obtained by computer simulations was far lower than that of the (1–10) surface.¹³⁸ Similarly Biermann *et al.* obtained surfaces with very different nature in terms of hydrophobicity/hydrophilicity of cellulose from molecular dynamics simulations.¹⁴² Using argon as a hydrophobic model, their simulations showed that argon or other hydrophobic species can easily dissolve.

Oxidation of the cellulose surface leads to changes in polarity. Lai *et al.* reported changes in the contact angle of bacterial cellulose before and after oxidation mediated by 2,2,6,6-tetramethylpiperidine-1-oxyl (TEMPO).¹⁴³ The authors correlated the change in hydrogen bonds with the changes in surface properties. Using XPS analysis to determine the O/C ratio on the cellulose surface and the relative amounts of different types of carbon–oxygen bonds, they found trends for both carbon and oxygen and showed that the –OH contribution decreases after oxidation. In addition, a slight increase of the contact angles was reported with the introduction of carboxylate groups at the surface of the bacterial cellulose fibers (Fig. 7).

An increase of the contact angles formed with water and glycerol was observed, being slightly more pronounced for the



Fig. 7 Contact angles of water (a) and glycerol (b) in pure BC and water (c) and glycerol (d) in oxidized BC, respectively. Droplets of 3 μL of water and glycerol were placed for 60 s over the BC films. (Adapted with permission from ref. 143: C. Lai, L. Sheng, S. Liao, T. Xi and Z. Zhang, Surface characterization of TEMPO-oxidized bacterial cellulose, *Surf. Interface Anal.*, 2013, **45**, 1673–1679. Copyright 2013, John Wiley & Sons, Ltd.)



swelling.¹⁵⁸ A clear illustration of the effect of ionization on swelling comes from the work of Lindström and Carlsson.¹⁵⁴ These authors noted that the water retention values of holo-cellulose and unbleached sulfate pulps show major increases as a function of pH in the range where carboxylic acid groups ionize; in this work also the relation to hornification was investigated. In line with the combination of hydrophobic and electrostatic interactions, Zhang *et al.* noted that addition of thiourea produces enhanced cellulose swelling in NaOH solutions.¹⁵⁹

In view of the discussed balance between hydrophobic and electrostatic interactions we can also expect large effects of addition of electrolytes where there is a large difference in polarity between the two ions. Thus we would expect combinations of high charge density cations like Ca^{2+} and Li^{+} with large polarizable anions like Γ^{-} and SCN^{-} to promote swelling. Indeed it was found for different cellulose fibers that LiSCN is very effective in enhancing swelling (see ref. 160 and references therein). We can interpret this as a weak association of the anions to cellulose whereas the cations are depleted. Similar effects were observed in recent studies dealing with wood impregnation by electrolytes.¹⁶¹ Furthermore, very important swelling was demonstrated using mixed solutions of NaSCN and urea.¹⁶²

Plasticization can in some ways be viewed as extreme swelling, gelation or partial dissolution of cellulose fibers; *i.e.* cellulose chain mobility increases drastically. Therefore, good plasticizing solvents should have similar properties as good dissolving agents. From this point of view, findings from 1943 of urea as a plasticizing agent are striking. This precedes by several decades the intense research on cold alkali-urea solvent systems and again suggests that weakening of the hydrophobic interactions between cellulose molecules has a key role.¹⁶³ Actually, plasticized or vulcanized paper was developed already in the 1860s.¹⁶⁴ It is made of several layers of paper, where each layer is impregnated by zinc chloride that has the capability to swell the cellulose fibers and partially dissolve it. After impregnation the layers are pressed together and zinc chloride is leached out through washing in several steps. Plasticized or vulcanized paperboards have improved mechanical properties compared to recycled paperboards. The improved mechanical properties expand the range of possible applications for products made of cellulose fibers and can be an alternative to plastics in some applications. Typically, plasticization increases density, mechanical strength and strain at break of the paper.¹⁶⁵ Normally the specific stiffness will be unchanged or increased.^{166,167} It is reported that vulcanized paper has excellent wear resistance, oil resistance, electrical insulation, thermal resistance and high wet strength.¹⁶⁴ The high density and low pore volume combined with a hydrophilic surface makes it also an excellent barrier for oil and fatty substances. The mechanical properties might also be sufficient for using it as a matrix in composites reinforced with glass or carbon fibers.¹⁶⁸

If the zinc chloride concentration is above 63 and below 72%, the crystalline structure of cellulose decreases. The higher the temperature is, the faster the crystalline cellulose will change to an amorphous structure.¹⁶⁹ At 65 °C a zinc chloride solution with a concentration of 73% by weight can dissolve cellulose.¹⁷⁰

This journal is © the Owner Societies 2017



Fig. 8 Stress–strain curves for paper made and simultaneously plasticized on a pilot paper machine. The paper was treated with zinc chloride and sodium hydroxide/urea, respectively, and testing was performed in the machine direction (MD) and cross direction (CD).

At concentrations below 62% of zinc chloride, the effect will be swelling of the cellulose fibers and partial dissolution.¹⁶⁹ After saturating the paper with zinc chloride, pressing will densify the paper and enable fiber-to-fiber bonds to develop. When zinc chloride is gradually washed out with water through a diffusion process and dried, the high density of the paper remains with improved mechanical properties compared to untreated paper. This is referred to as vulcanization and the fibers will be strongly bonded to each other.¹⁶⁶ In Fig. 8 one example of how the mechanical properties of paperboard made from dissolving pulp change after solvent plasticization is shown. Both stress at peak load and strain at break increase when the NaOH/urea at -12°C or ZnCl_2 solution is added to the paper web in a size press on the pilot paper machine. Most likely, the mechanical properties of the plasticized paper made on the pilot machine can be further improved by tuning the time, temperature and washing of the treatment.

Plasticization partly changes the crystallinity of cellulose fibers from cellulose I to cellulose II, and increases the amorphous cellulose content, thereby changing the fiber and paper properties.¹⁷¹ Furthermore, plasticization increases the fiber-to-fiber bond strength. Plasticization of the surface layers of the cellulose fibers induces higher strain at break, stiffness and tensile strength.^{172,173} The solvent used for plasticizing makes the surface of the cellulose fibers soft and swells the fibers. However, rigorous washing of the paper to remove the solvent, and subsequent drying, might lead to shrinkage in all directions.¹⁶⁴ Moreover, the density of the paper increases as the fibers come together and develop strong bonds between them. The tensile strength and stiffness are higher for cellulose I than II.¹⁷⁴ Native cellulose I has a chain modulus of elasticity of 138 GPa and a strength of several GPa.¹⁷⁴ Because of finite crystalline length of the cellulose molecule and fibril agglomeration the effective elastic modulus of cellulose nanofibrils (CNF) will be less and is calculated to be *ca.* 30–65 GPa.¹⁷⁵ Cellulose II has a tensile strength of up to 1.8 GPa and an elastic modulus of 55 GPa when spun into fibers.¹⁷⁴ This stretched regenerated fiber is highly oriented, so the corresponding tensile stiffness

and strength for an in-plane isotropic material should be about 1/3 of these values.



Cellulose as a dispersion stabilizer

Using natural products with minimal modification is a strong driving force in developing biocompatible, biodegradable and nontoxic formulations. Important stabilizers of disperse systems are amphiphilic molecules. The efficient creation of an emulsion generally requires an emulsifier, which facilitates dispersion by lowering the interfacial tension, and a stabilizer that prevents flocculation of droplets by creating repulsion between droplets. Typically, a surfactant is used as dispersant and a polymer as stabilizer; some amphiphilic polymers, notably block copolymers, can fulfil both criteria. Cellulose derivatives, such as methyl cellulose, hydroxyethyl cellulose and ethyl hydroxyethyl cellulose, are well known as efficient stabilizers of emulsions (and suspensions). This highlights their amphiphilic nature which is clearly not a solo effect of the different chemical modifications but a direct consequence of the native cellulose backbone. In arguing that cellulose itself should be considered as an amphiphilic polymer we would naturally expect that cellulose would locate at the oil–water interfaces in an emulsion and thus acting as a good stabilizer; similar considerations concern other disperse systems like foams. This would represent a clear advantage to use native cellulose without the need of chemical modifications.

The introduction of cellulose in emulsions must, as an initial step, involve its dissolution for the reasons elaborated before. Several solvents can be considered but it is an obvious advantage to use aqueous systems since the water used for dissolution can remain as either the dispersed phase or the dispersion medium in the emulsion; any other solvent would need to be removed involving a more complex process. Work on using dissolved cellulose for emulsions has been pioneered by Cohen's group in Haifa. Rein *et al.* used regenerated cellulose as a novel and efficient eco-friendly emulsifying agent.^{176,177} These authors suggest that the hydrophilic hydroxyl groups interact with the water while the more hydrophobic planes of the glucopyranose rings are located towards the hydrocarbon oil; besides, the dissolution–regeneration process facilitates the formation of an encapsulating coating at the water–oil interface because of the afforded higher mobility of the cellulose molecules. The authors demonstrated that regenerated cellulose can stabilize both oil-in-water and water-in-oil emulsions. Although the latter were found to be less stable, phase separation was only observed after several months. In the case of oil-in-water emulsions, stability was attained for one year, where neither flocculation nor coalescence was observed. The solvent used for cellulose was the ionic liquid EmimAc, and deionized water was used as a coagulant. Another research group has started exploring the role of regenerated cellulose as an emulsion stabilizer, but using an aqueous phosphoric acid solution as the cellulose solvent and deionized water as a coagulant.^{178,179} Cohen's group used two different methods to obtain the emulsions: (1) dispersing the oil directly in the cellulose solution and adding excess of water



An emulsification procedure has been recently developed by some of us starting with an aqueous solution with dissolved cellulose in an 85 wt% phosphoric acid solution. This solution was then used as a dispersion medium for oil, which was



Conclusions

This journal is © the Owner Societies 2017

interactions are affected. Strong arguments arise from cellulose structural features as well as from the behaviour of cellulose derivatives in solution that considerably pales down the overrated hydrogen bonding mechanism. Systems such as TBAH and NaOH + urea are good examples intensely studied in recent years, which show how amphiphilicity (the tetrabutylammonium cation is markedly amphiphilic while urea is a known weakener of hydrophobic interactions) and extreme pH (strong alkaline systems can partially ionize cellulose) are beneficial for efficient dissolution. In view of the enormous literature on differences in solubility between ionic and nonionic polymers and the understanding of this in terms of simple electrostatic interactions it is surprising that the literature on cellulose dissolution is essentially devoid of attributions to ionization effects, *i.e.* either protonation or deprotonation. The same can be said for swelling, although the early literature, where ionization of cellulose is considered, constitutes a notable exception. This interplay between different interactions is crucial to understand and control other phenomena such as gelation/regeneration, wetting or stabilization of dispersions.

Acknowledgements

This work was financially supported by Södra Skogsägarnas Stiftelse, Stiftelsen Nils och Dorthi Troëdssons forskningsfond, and the Swedish Research Council. The Portuguese Foundation for Science and Technology (FCT) is acknowledged through the project PTDC/AGR-TEC/4814/2014 and researcher grant IF/01005/2014. "The Coimbra Chemistry Centre" is supported by FCT through the programmes UID/QUI/UI0313/2013 and COMPETE. Financial support from the Swedish Research Council VR, grant no. 2015-04290 and funding from WoodWisdom-ERA *via* the Swedish Governmental Agency for Innovation, VINNOVA, grant no. 2013-05617 are gratefully acknowledged. Dr Isabel Mira and Dr Jan-Willem Benjamins from RISE Bioscience and Materials are acknowledged for their support on the dynamic surface tension and interfacial rheology tests. Dr Bo Westerlind is thanked for the stress-strain measurements.

References

- 1 N. Gralen, *Nature*, 1943, **152**, 625.
- 2 T. Svedberg, *J. Phys. Colloid Chem.*, 1947, **51**, 1–18.
- 3 H. Staudinger, *Naturwissenschaften*, 1934, **32**, 813–819.
- 4 *Cellulose and Cellulose Derivatives*, ed. E. Ott, M. Spurlin and M. W. Grafflin, Interscience Publishers, New York, 2nd edn, 1955, vol. V.
- 5 C. Beadle and H. P. Stevens, *The 8th International Congress on Applied Chemistry, The influence of temperature on the hydration and absorption of alkali by regenerated cellulose*, 1912, vol. 18, p. 25.
- 6 M. S. Neale, *J. Text. Inst.*, 1929, **20**, T373–T400.
- 7 H. Sobue, H. Kiessig and K. Hess, *Z. Phys. Chem., Abt. B*, 1939, **43**, 309–328.
- 8 H. Staudinger and R. Mohr, *J. Prakt. Chem.*, 1941, **158**, 233–244.
- 9 P. H. Hermans, *J. Phys. Chem.*, 1941, **45**, 827–836.
- 10 K. Kamide, K. Okajima, T. Matsui and K. Kowsaka, *Polym. J.*, 1984, **16**, 857–866.
- 11 J. Cai and L. Zhang, *Macromol. Biosci.*, 2005, **5**, 539–548.
- 12 J. Cai, L. N. Zhang, J. P. Zhou, H. S. Qi, H. Chen, T. Kondo, X. M. Chen and B. Chu, *Adv. Mater.*, 2007, **19**, 821–825.
- 13 L. N. Zhang, D. Ruan and S. J. Gao, *J. Polym. Sci., Part B: Polym. Phys.*, 2002, **40**, 1521–1529.
- 14 J. Cai, L. Zhang, S. L. Liu, Y. T. Liu, X. J. Xu, X. M. Chen, B. Chu, X. L. Guo, J. Xu, H. Cheng, C. C. Han and S. Kuga, *Macromolecules*, 2008, **41**, 9345–9351.
- 15 J. P. Zhou and L. N. Zhang, *Polym. J.*, 2000, **32**, 866–870.
- 16 L. N. Zhang, D. Ruan and J. P. Zhou, *Ind. Eng. Chem. Res.*, 2001, **40**, 5923–5928.
- 17 C. L. McCormick and D. K. Lichatowich, *J. Polym. Sci., Part B: Polym. Lett.*, 1979, **17**, 479–484.
- 18 C. Graenacher, *US Pat.*, 1943176, 1934.
- 19 C. Graenacher and R. Sallmann, *US Pat.*, 2179181, assigned to Society of Chemical Industry, Basel, 1939.
- 20 D. J. Johnson, *US Pat.*, 3447939, assigned to Eastman Kodak, 1969.
- 21 C. C. McCorsely and J. K. Varga, *US Pat.*, 4142913, assigned to Akzona Inc, 1979.
- 22 N. E. Franks and J. K. Varga, *US Pat.*, 4145532, assigned to Akzona Inc, 1979.
- 23 H. P. Fink, P. Weigel, H. J. Purz and J. Ganster, *Prog. Polym. Sci.*, 2001, **26**, 1473–1524.
- 24 B. Lindman, G. Karlström and L. Stigsson, *J. Mol. Liq.*, 2010, **156**, 76–81.
- 25 B. Medronho, A. Romano, M. G. Miguel, L. Stigsson and B. Lindman, *Cellulose*, 2012, **19**, 581–587.
- 26 W. G. Glasser, R. H. Atalla, J. Blackwell, R. M. Brown, W. Burchard, A. D. French, D. O. Klemm and Y. Nishiyama, *Cellulose*, 2012, **19**, 589–598.
- 27 Y. Nishiyama, P. Langan and H. Chanzy, *J. Am. Chem. Soc.*, 2002, **124**, 9074–9082.
- 28 A. D. French, D. P. Miller and A. Aabloo, *Int. J. Biol. Macromol.*, 1993, **15**, 30–36.
- 29 A. D. French, M. K. Dowd, S. K. Cousins, R. M. Brown and D. P. Miller, *Enzymatic Degradation of Insoluble Carbohydrates*, 1995, **618**, 13–37.
- 30 S. K. Cousins and R. M. Brown, *Polymer*, 1995, **36**, 3885–3888.
- 31 M. Bergensträhle, J. Wohler, M. E. Himmel and J. W. Brady, *Carbohydr. Res.*, 2010, **345**, 2060–2066.
- 32 R. Parthasarathi, G. Bellesia, S. P. S. Chundawat, B. E. Dale, P. Langan and S. Gnanakaran, *J. Phys. Chem. A*, 2011, **115**, 14191–14202.
- 33 Y. Bao, H. J. Qian, Z. Y. Lu and S. Cui, *Macromolecules*, 2015, **48**, 3685–3690.
- 34 B. Medronho, H. Duarte, L. Alves, F. E. Antunes, A. Romano and B. Lindman, *Nord. Pulp Pap. Res. J.*, 2015, **30**, 58–66.
- 35 I. Diddens, B. Murphy, M. Krisch and M. Müller, *Macromolecules*, 2008, **41**, 9755–9759.
- 36 O. Biermann, E. Hadicke, S. Koltzenburg and F. Muller-Plathe, *Angew. Chem., Int. Ed.*, 2001, **40**, 3822–3825.
- 37 C. Yamane, T. Aoyagi, M. Ago, K. Sato, K. Okajima and T. Takahashi, *Polym. J.*, 2006, **38**, 819–826.



- 38 H. Miyamoto, M. Umemura, T. Aoyagi, C. Yamane, K. Ueda and K. Takahashi, *Carbohydr. Res.*, 2009, **344**, 1085–1094.
- 39 O. L. Sponsler, *Protoplasma*, 1931, **12**, 241–255.
- 40 J. O. Warwicker and A. C. Wright, *J. Appl. Polym. Sci.*, 1967, **11**, 659–671.
- 41 C. Tanford, *J. Am. Chem. Soc.*, 1964, **86**, 2050–2059.
- 42 R. Zangi, R. H. Zhou and B. J. Berne, *J. Am. Chem. Soc.*, 2009, **131**, 1535–1541.
- 43 J. Piercy, M. N. Jones and G. Ibbotson, *J. Colloid Interface Sci.*, 1971, **37**, 165–170.
- 44 G. Briganti, S. Puvvada and D. Blankschtein, *J. Phys. Chem.*, 1991, **95**, 8989–8995.
- 45 M. A. Behrens, J. A. Holdaway, P. Nosrati and U. Olsson, *RSC Adv.*, 2016, **6**, 30199–30204.
- 46 M. Gubitosi, H. Duarte, L. Gentile, U. Olsson and B. Medronho, *Biomacromolecules*, 2016, **17**, 2873–2881.
- 47 C. H. Haigler, R. Malcolmbrown and M. Benziman, *Science*, 1980, **210**, 903–906.
- 48 C. H. Haigler, A. R. White, R. M. J. Brown and K. M. Cooper, *J. Cell Biol.*, 1982, **94**, 64–69.
- 49 R. P. Swatloski, S. K. Spear, J. D. Holbrey and R. D. Rogers, *J. Am. Chem. Soc.*, 2002, **124**, 4974–4975.
- 50 S. D. Zhu, Y. X. Wu, Q. M. Chen, Z. N. Yu, C. W. Wang, S. W. Jin, Y. G. Ding and G. Wu, *Green Chem.*, 2006, **8**, 325–327.
- 51 M. Abe, K. Kuroda and H. Ohno, *ACS Sustainable Chem. Eng.*, 2015, **3**, 1771–1776.
- 52 R. C. Remsing, R. P. Swatloski, R. D. Rogers and G. Moyna, *Chem. Commun.*, 2006, 1271–1273, DOI: 10.1039/B600586c.
- 53 R. C. Remsing, G. Hernandez, R. P. Swatloski, W. W. Massefski, R. D. Rogers and G. Moyna, *J. Phys. Chem. B*, 2008, **112**, 11071–11078.
- 54 B. Lindman, S. Forsen and E. Forslind, *J. Phys. Chem.*, 1968, **72**, 2805–2813.
- 55 B. Lindman, H. Wennerstrom and S. Forsen, *J. Phys. Chem.*, 1970, **74**, 754–760.
- 56 H. Wennerstrom, B. Lindman and S. Forsen, *J. Phys. Chem.*, 1971, **75**, 2936–2942.
- 57 B. Lindman, H. Wennerstrom and S. Forsen, *J. Phys. Chem.*, 1992, **96**, 5669–5670.
- 58 K. M. Gupta, Z. Q. Hu and J. W. Jiang, *Polymer*, 2011, **52**, 5904–5911.
- 59 W. Burchard, *Cellulose*, 2003, **10**, 213–225.
- 60 E. Kontturi, T. Tammelin and M. Osterberg, *Chem. Soc. Rev.*, 2006, **35**, 1287–1304.
- 61 C. Zhang, R. G. Liu, J. F. Xiang, H. L. Kang, Z. J. Liu and Y. Huang, *J. Phys. Chem. B*, 2014, **118**, 9507–9514.
- 62 K. Kamide, K. Kowsaka and K. Okajima, *Polym. J.*, 1985, **17**, 707–711.
- 63 K. Kamide, K. Yasuda, T. Matsui, K. Okajima and T. Yamashiki, *Cellul. Chem. Technol.*, 1990, **24**, 23–31.
- 64 T. Yamashiki, T. Matsui, M. Saitoh, K. Okajima and K. Kamide, *Br. Polym. J.*, 1990, **22**, 73–83.
- 65 T. Yamashiki, T. Matsui, M. Saitoh, K. Okajima and K. Kamide, *Br. Polym. J.*, 1990, **22**, 121–128.
- 66 T. Yamashiki, T. Matsui, M. Saitoh, Y. Matsuda, K. Okajima, K. Kamide and T. Sawada, *Br. Polym. J.*, 1990, **22**, 201–212.
- 67 K. Kamide and K. Okajima, *Cellulose dope, process for preparation and method for application thereof*, US Pat., 4634470, 1987.
- 68 K. Kamide, K. Okajima and K. Kowsaka, *Polym. J.*, 1992, **24**, 71–86.
- 69 Y. Cao and T. Huimin, *Appl. Microbiol. Biotechnol.*, 2006, **70**, 176–182.
- 70 L. Rahkamo, M. SiikaAho, M. Vehvilainen, M. Dolk, L. Viikari, P. Nousiainen and J. Buchert, *Cellulose*, 1996, **3**, 153–163.
- 71 J. M. Zhang, H. Zhang, J. Wu, J. Zhang, J. S. He and J. F. Xiang, *Phys. Chem. Chem. Phys.*, 2010, **12**, 1941–1947.
- 72 H. Zhang, J. Wu, J. Zhang and J. S. He, *Macromolecules*, 2005, **38**, 8272–8277.
- 73 A. Brandt, J. Grasvik, J. P. Hallett and T. Welton, *Green Chem.*, 2013, **15**, 550–583.
- 74 M. Zavrel, D. Bross, M. Funke, J. Buchs and A. C. Spiess, *Bioresour. Technol.*, 2009, **100**, 2580–2587.
- 75 Y. Fukaya, K. Hayashi, M. Wada and H. Ohno, *Green Chem.*, 2008, **10**, 44–46.
- 76 L. Crowhurst, P. R. Mawdsley, J. M. Perez-Arlandis, P. A. Salter and T. Welton, *Phys. Chem. Chem. Phys.*, 2003, **5**, 2790–2794.
- 77 A. Brandt, J. P. Hallett, D. J. Leak, R. J. Murphy and T. Welton, *Green Chem.*, 2010, **12**, 672–679.
- 78 T. Liebert, *Acs Sym Ser*, 2009, vol. 1033, pp. 3–54.
- 79 B. Medronho and B. Lindman, *Curr. Opin. Colloid Interface Sci.*, 2014, **19**, 32–40.
- 80 T. Budtova and P. Navard, *Cellulose*, 2016, **23**, 5–55.
- 81 C. Roy, T. Budtova, P. Navard and O. Bedue, *Biomacromolecules*, 2001, **2**, 687–693.
- 82 M. Egal, T. Budtova and P. Navard, *Cellulose*, 2008, **15**, 361–370.
- 83 J. P. Zhou, Y. Qin, S. L. Liu and L. Zhang, *Macromol. Biosci.*, 2006, **6**, 84–89.
- 84 J. P. Zhou, L. N. Zhang and J. Cai, *J. Polym. Sci., Part B: Polym. Phys.*, 2004, **42**, 347–353.
- 85 J. P. Zhou, L. Zhang, J. Cai and H. Shu, *J. Membr. Sci.*, 2002, **210**, 77–90.
- 86 Q. Zhou, L. N. Zhang, M. Li, X. J. Wu and G. Z. Cheng, *Polym. Bull.*, 2005, **53**, 243–248.
- 87 H. S. Qi, Q. L. Yang, L. N. Zhang, T. Liebert and T. Heinze, *Cellulose*, 2011, **18**, 237–245.
- 88 S. Schneider and P. Linse, *J. Phys. Chem. B*, 2003, **107**, 8030–8040.
- 89 S. Schneider and P. Linse, *Eur. Phys. J. E: Soft Matter Biol. Phys.*, 2002, **8**, 457–460.
- 90 A. G. Wilkes, in *The viscose process*, ed. C. Woodings, Regenerated cellulose fibres, Woodhead Publishing, Cambridge, 2001.
- 91 S. Wang, A. Lu and L. N. Zhang, *Prog. Polym. Sci.*, 2016, **53**, 169–206.
- 92 A. Isogai, *Cellulose*, 1997, **4**, 99–107.
- 93 L. Alves, B. Medronho, F. E. Antunes, D. Topgaard and B. Lindman, *Carbohydr. Polym.*, 2016, **151**, 707–715.
- 94 B. Medronho, H. Duarte, L. Alves, F. E. Antunes, A. Romano and A. J. M. Valente, *Carbohydr. Polym.*, 2016, **140**, 136–143.



- 95 L. Alves, B. Medronho, F. E. Antunes, D. Topgaard and B. Lindman, *Cellulose*, 2016, **23**, 247–258.
- 96 L. Gentile and U. Olsson, *Cellulose*, 2016, **23**, 2753–2758.
- 97 R. Fuchs, N. Habermann and P. Klüfers, *Angew. Chem.*, 1993, **105**, 895.
- 98 W. Burchard, N. Habermann, P. Klüfers, B. Seger and U. Wilhelm, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 884–887.
- 99 P. Klüfers and J. Schuhmacher, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 1742–1744.
- 100 K. Saalwachter, W. Burchard, P. Klüfers, G. Kettenbach, P. Mayer, D. Klemm and S. Dugarmaa, *Macromolecules*, 2000, **33**, 4094–4107.
- 101 E. Bialik, B. Stenqvist, Y. Fang, A. Ostlund, I. Furo, B. Lindman, M. Lund and D. Bernin, *J. Phys. Chem. Lett.*, 2016, **7**, 5044–5048.
- 102 B. Xiong, P. P. Zhao, P. Cai, L. N. Zhang, K. Hu and G. Z. Cheng, *Cellulose*, 2013, **20**, 613–621.
- 103 Z. J. Liu, C. Zhang, R. G. Liu, W. S. Zhang, H. L. Kang, P. P. Li and Y. Huang, *Cellulose*, 2016, **23**, 295–305.
- 104 E. Bialik, “personal communication”, 2016.
- 105 *The European polysaccharide network of excellence (EPNOE)*, ed. P. Navard, Springer, Wien, 2012.
- 106 M. Malmsten and B. Lindman, *Langmuir*, 1990, **6**, 357–364.
- 107 B. Lindman, A. Carlsson, G. Karlstrom and M. Malmsten, *Adv. Colloid Interface Sci.*, 1990, **32**, 183–203.
- 108 A. Carlsson, G. Karlstrom and B. Lindman, *Langmuir*, 1986, **2**, 536–537.
- 109 A. Carlsson, G. Karlstrom and B. Lindman, *J. Phys. Chem.*, 1989, **93**, 3673–3677.
- 110 A. Carlsson, G. Karlstrom, B. Lindman and O. Stenberg, *Colloid Polym. Sci.*, 1988, **266**, 1031–1036.
- 111 A. V. Svensson, L. G. Huang, E. S. Johnson, T. Nylander and L. Piculell, *ACS Appl. Mater. Interfaces*, 2009, **1**, 2431–2442.
- 112 J. Sjostrom and L. Piculell, *Langmuir*, 2001, **17**, 3836–3843.
- 113 B. Lindman, B. Medronho and G. Karlström, *Curr. Opin. Colloid Interface Sci.*, 2016, **22**, 23–29.
- 114 K. Thuresson and B. Lindman, *Colloids Surf., A*, 1999, **159**, 219–226.
- 115 B. Cabane, K. Lindell, S. Engstrom and B. Lindman, *Macromolecules*, 1996, **29**, 3188–3197.
- 116 M. Nyden and O. Soderman, *Macromolecules*, 1998, **31**, 4990–5002.
- 117 E. Freyssingas, K. Thuresson, T. Nylander, F. Joabsson and B. Lindman, *Langmuir*, 1998, **14**, 5877–5889.
- 118 M. Andersson and B. Wittgren, “personal communication”.
- 119 B. Medronho and B. Lindman, *Adv. Colloid Interface Sci.*, 2015, **222**, 502–508.
- 120 P. Singh, H. Duarte, L. Alves, F. Antunes, N. Le Moigne, J. Dormanns, B. Duchemin, M. P. Staiger and M. Medronho, in *From Cellulose Dissolution and Regeneration to Added Value Applications – Synergism Between Molecular Understanding and Material Development, Cellulose – Fundamental Aspects and Current Trends*, ed. M. Poletto, InTech, 2015, DOI: 10.5772/61402.
- 121 D. Klemm, B. Heublein, H. P. Fink and A. Bohn, *Angew. Chem., Int. Ed.*, 2005, **44**, 3358–3393.
- 122 T. C. Shen and I. Cabasso, *Macromolecular solutions, solvent-property relationship in polymers*, ed. R. B. Seymour and G. A. Stahl, Pergamon Press, New York, 1982.
- 123 N. Isobe, S. Kimura, M. Wada and S. Kuga, *Carbohydr. Polym.*, 2012, **89**, 1298–1300.
- 124 H. Leipner, S. Fischer, E. Brendler and W. Voigt, *Macromol. Chem. Phys.*, 2000, **201**, 2041–2049.
- 125 K. M. Gupta, Z. Q. Hu and J. W. Jiang, *RSC Adv.*, 2013, **3**, 12794–12801.
- 126 K. M. Gupta and J. W. Jiang, *Chem. Eng. Sci.*, 2015, **121**, 180–189.
- 127 Z. D. Ding, Z. Chi, W. X. Gu, S. M. Gu, J. H. Liu and H. J. Wang, *Carbohydr. Polym.*, 2012, **89**, 7–16.
- 128 R. Li, L. N. Zhang and M. Xu, *Carbohydr. Polym.*, 2012, **87**, 95–100.
- 129 S. Zhang, F. X. Li and J. Y. Yu, *Cellul. Chem. Technol.*, 2011, **45**, 593–604.
- 130 H. Miyamoto, M. Ago, C. Yamane, M. Seguchi, K. Ueda and K. Okajima, *Carbohydr. Res.*, 2011, **346**, 807–814.
- 131 J. Hayashi, S. Masuda and S. Watanabe, *Nippon Kagaku Kaishi*, 1974, 948–954.
- 132 P. H. Hermans, *J. Polym. Sci.*, 1949, **4**, 145–151.
- 133 S. K. Cousins and R. M. Brown, *Polymer*, 1997, **38**, 897–902.
- 134 S. K. Cousins and R. M. Brown, *Polymer*, 1997, **38**, 903–912.
- 135 W. Burchard, *Adv. Colloid Interface Sci.*, 1996, **64**, 45–65.
- 136 J. L. Wertz, J. P. Mercier and O. Bédúe, *Cellulose Science and Technology*, EPFL Press, Boca Raton, 1st edn, 2010.
- 137 A. Keller, *Faraday Discuss.*, 1979, **68**, 145–166.
- 138 C. Yamane, T. Aoyagi, M. Ago, K. Sato, K. Okajima and T. Takahashi, *Polym. J.*, 2006, **38**, 819–826.
- 139 H. S. Whang and B. S. Gupta, *Text. Res. J.*, 2000, **70**, 351–358.
- 140 X. Geng and W. A. Henderson, *RSC Adv.*, 2014, **4**, 31226–31229.
- 141 J. Bajdik, G. Regdon Jr, T. Marek, I. Erős, K. Süvegh and K. Pintye-Hódi, *Int. J. Pharm.*, 2005, **301**, 192–198.
- 142 O. Biermann, E. Hädicke, S. Koltzenburg and F. Müller-Plathe, *Angew. Chem., Int. Ed.*, 2001, **40**, 3822–3825.
- 143 C. Lai, L. Y. Sheng, S. B. Liao, T. F. Xi and Z. X. Zhang, *Surf. Interface Anal.*, 2013, **45**, 1673–1679.
- 144 C. Nägeli, *Sitzber Bay Akad Wiss München*, 1864, **1**, 282–323.
- 145 G. Penetier, *Bull. Soc. Ind. Rouen*, 1883, **11**, 235–237.
- 146 N. Fleming and A. C. Thaysen, *Biochem. J.*, 1920, **14**, 25–28.
- 147 N. Fleming and A. C. Thaysen, *Biochem. J.*, 1921, **15**, 407–414.
- 148 V. W. Tripp and M. L. Rollins, *Anal. Chem.*, 1952, **24**, 1721–1728.
- 149 C. W. Hock, in *Microscopic structure*, ed. E. Ott, H. M. Spurlin and M. W. Grafflin, Cellulose and cellulose derivatives (part 1), Interscience, New York, 2nd edn, 1954, pp. 347–392.
- 150 J. O. Warwicker, R. Jeffries, R. L. Colbran and R. N. Robinson, *A review of the literature on the effect of caustic soda and other swelling agents on the fine structure of cotton*, Shirley Institute Pamphlet No. 93, St Ann's Press, England, 1966.
- 151 H. Chanzy, P. Noe, M. Paillet and P. Smith, *J. Appl. Polym. Sci.*, 1983, **37**, 239–259.
- 152 C. Cuissinat and P. Navard, *Macromol. Symp.*, 2006, **244**, 1–18.
- 153 J. T. Marsh, *An introduction to the chemistry of cellulose*, Chapman & Hall, London, 2nd edn, 1942.
- 154 T. Lindström and G. Carlsson, *Sven. Papperstidn.*, 1982, **85**, R146–R151.



- 155 A. M. Scallan, *Tappi J.*, 1983, **66**, 73–75.
- 156 S. Katz, N. Liebergott and A. M. Scallan, *Tappi*, 1981, **64**, 97–100.
- 157 S. Katz and A. M. Scallan, *Tappi J.*, 1983, **66**, 85–87.
- 158 P. F. Nelson and C. G. Kalkipsakis, *Tappi J.*, 1964, **47**, 107.
- 159 S. Zhang, W.-C. Wang, F.-X. Li and J.-Y. Yu, *Cellul. Chem. Technol.*, 2013, **47**, 671–679.
- 160 A. Ehrhardt, S. Groner and T. Bechtold, *Fibres Text. East. Eur.*, 2007, **15**, 46–48.
- 161 L. Bertinetti, A. Masic, R. Schuetz, A. Barbetta, B. Seidt, W. Wagermaier and P. Fratzl, *J. Mech. Behav. Biomed. Mater.*, 2015, **52**, 14–21.
- 162 A. Mahmud-Ali and T. Bechtold, *Carbohydr. Polym.*, 2015, **116**, 124–130.
- 163 F. P. L. (U.S.), *Forest products laboratory urea-plasticized wood (uralloy)*, Madison, Wis.: U.S. Dept. of Agriculture, Forest Service, Forest Products Laboratory, 1943.
- 164 W. F. Brown, *Vulcanized fibre-an old material with a new relevancy*, In *Electrical Insulation Conference and Electrical Manufacturing and Coil Winding Conference*, 1999.
- 165 H. Halonen, *Structural changes during cellulose composite processing*, PhD thesis, Department of Fibre and Polymer Technology, KTH, Stockholm, 2012.
- 166 B. Künne and D. Dumke, *Vulcanized fiber as a high-strength construction material for highly loaded construction units. in International Paper Physics Conference & 8th International Paper and Coating Chemistry Symposium*, Stockholm, 2012.
- 167 P. A. Larsson, L. A. Berglund and L. Wagberg, *Cellulose*, 2014, **21**, 323–333.
- 168 H. B. Fay, *Reinforced vulcanized fiber backing belt*, US Pat., US2293246, 1942.
- 169 N. J. Richards, *The Aqueous Zinc Chloride System and its Complex Formation with Cellulose-Related Compounds*, 1969.
- 170 Q. Xu and L.-F. Chen, *Textile Technology International*, 1996, 19–21.
- 171 P. Piltanen, N. C. Hildebrandt, B. Westerlind, J. P. Valkama, T. Tervahartiala and M. Illikainen, *Compos. Sci. Technol.*, 2016, **135**, 153–158.
- 172 N. Soykeabkaew, N. Arimoto, T. Nishino and T. Peijs, *Compos. Sci. Technol.*, 2008, **68**, 2201–2207.
- 173 T. Nishino and N. Arimoto, *Biomacromolecules*, 2007, **8**, 2712–2716.
- 174 W. Gindl and J. Keckes, *J. Appl. Polym. Sci.*, 2007, **103**, 2703–2708.
- 175 M. C. Nygård, C. Fellers and S. Östlund, *Development of the notched shear test. Advances in pulp and paper research*, Transactions of the 14th Fundamental Research Symposium Oxford, September 14–18, 2009.
- 176 D. M. Rein, R. Khalfin and Y. Cohen, *J. Colloid Interface Sci.*, 2012, **386**, 456–463.
- 177 S. Napso, D. M. Rein, R. Khalfin, O. Kleinerman and Y. Cohen, *Colloids Surf., B*, 2016, **137**, 70–76.
- 178 X. J. Jia, Y. W. Chen, C. Shi, Y. F. Ye, P. Wang, X. X. Zeng and T. Wu, *J. Agric. Food Chem.*, 2013, **61**, 12405–12414.
- 179 X. J. Jia, R. R. Xu, W. Shen, M. X. Xie, M. Abid, S. Jabbar, P. Wang, X. X. Zeng and T. Wu, *Food Hydrocolloids*, 2015, **43**, 275–282.
- 180 W. Shen, L. Guo, T. Wu, W. H. Zhang and M. Abid, *LWT–Food Sci. Technol.*, 2016, **72**, 292–301.
- 181 E. Melzer, J. Kreuter and R. Daniels, *Eur. J. Pharm. Biopharm.*, 2003, **56**, 23–27.
- 182 W. B. Sun, D. J. Sun, Y. P. Wei, S. Y. Liu and S. Y. Zhang, *J. Colloid Interface Sci.*, 2007, **311**, 228–236.
- 183 I. Kalashnikova, H. Bizot, B. Cathala and I. Capron, *Langmuir*, 2011, **27**, 7471–7479.
- 184 K. R. Peddiredy, T. Nicolai, L. Benyahia and I. Capron, *ACS Macro Lett.*, 2016, **5**, 283–286.

