

Cite this: *Chem. Sci.*, 2019, 10, 191 All publication charges for this article have been paid for by the Royal Society of Chemistry

Manganese(II) phosphate nanosheet assembly with native out-of-plane Mn centres for electrocatalytic water oxidation†

Hongfei Liu,^{‡a} Xueqing Gao,^{‡a} Xiaolong Yao,^{‡b} Mingxing Chen,^c Guojun Zhou,^a Jing Qi,^a Xueli Zhao,^a Weichao Wang,^{id}*^b Wei Zhang,^{id}*^a and Rui Cao,^{id}*^{ac}

Nature selects Mn-clusters as catalysts for water oxidation, which is a significant reaction in photosynthesis. Thus, it is of critical importance to develop Mn-based superstructures and study their catalytic details for water-splitting-based renewable energy research. Herein, we report a manganese(II) phosphate nanosheet assembly with asymmetric out-of-plane Mn centers from the transformation of amine-intercalated nanoplates for efficient electrocatalytic water oxidation in neutral aqueous solutions. From structural and computational studies, it is found that the native out-of-plane Mn centers with terminal water ligands are accessible and preferential oxidation sites to form active intermediates for water oxidation. In addition, the asymmetry can stabilize the key Mn^{III} intermediate, as demonstrated by electrochemical and spectrometric studies. This study delivers a convenient strategy to prepare unique nanosheet assemblies for electrocatalysis and fundamental understandings of oxygen evolution chemistry.

Received 22nd August 2018

Accepted 1st October 2018

DOI: 10.1039/c8sc03764g

rsc.li/chemical-science

Introduction

Hydrogen is an energy carrier with high gravimetric energy density. Compared with traditional methods, electrocatalytic water splitting by sustainable electricity represents a green approach to produce hydrogen.^{1,2} In water splitting, the oxygen evolution reaction (OER) is challenging due to the high energy barriers for the breaking of O–H bonds and the attendant formation of O–O bonds.³ Thus, it is significant to understand the inherent limiting factors of the OER toward advanced water splitting. Interestingly, natural systems selected Mn-based clusters as water oxidation catalysts to produce oxygen powerfully under neutral conditions.^{4,5} Therefore, studies on Mn-based catalysts are critical to understand the detailed mechanism of water oxidation and to guide the development of functional artificial water splitting systems.

A variety of MnO_x polymorphs have been developed for chemical, electrochemical and photochemical water oxidations.^{6–9} The framework structure, Mn geometry, Mn valence and surface structure are mutually important for the efficiency

of water oxidation.^{10–13} Substantial Mn-based oxide catalysts transform into layered structures with out-of-plane or boundary undercoordinated units as effective catalytic sites,^{14,15} which has been further demonstrated by detailed computational studies and X-ray absorption spectroscopy analyses by Mattioli and co-workers.¹⁶ These active centres are typically associated with lattice defects. Therefore, it will be very promising and challenging to rationally design Mn-based materials with native out-of-plane Mn centres for the OER, which has yet not been reported to the best of our knowledge. In addition, it is generally acknowledged that the Mn^{III} species is the key catalytic intermediate for the OER.^{17,18} Dismukes and co-workers present detailed studies on the coordination geometry of Mn^{III} sites as the origin of the OER activity in several Mn-based materials. Specifically, the flexible out-of-plane corner-sharing Mn³⁺O₆ sites are substantially more active than buried edge-sharing Mn³⁺O₆ centres.¹⁰ Recently, Nocera and co-workers also reported the introduction of Mn^{III} into an activated δ-MnO₂ film.¹⁹ However, the major problem of the OER-active Mn^{III} species is its instability in a symmetric octahedral geometry. In many Mn-based oxides, Mn^{III} has an electronic configuration of t_{2g}³e_g¹, which can induce significant Jahn–Teller (J–T) distortion.^{20,21} In neutral solutions, Mn^{III} intermediates are inclined to disproportionate into Mn^{II} and Mn^{IV} species, neither of which is a significant contributor in water oxidation.^{22,23} To address this issue, asymmetry was introduced into the Mn geometry.²⁴ The asymmetry in the crystal frameworks can tolerate J–T distortion and thereby stabilize the Mn^{III} intermediate. Thus, we are interested in bringing structural asymmetry in Mn-based materials with native out-of-plane Mn centres for the OER.

^aKey Laboratory of Applied Surface and Colloid Chemistry, Ministry of Education, School of Chemistry and Chemical Engineering, Shaanxi Normal University, Xi'an 710119, China. E-mail: zw@snnu.edu.cn; ruicao@ruc.edu.cn

^bDepartment of Electronics, Nankai University, Tianjin 300071, China. E-mail: weichaowang@nankai.edu.cn

^cDepartment of Chemistry, Renmin University of China, Beijing 100872, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8sc03764g

‡ These authors contributed equally to this work.



correlate almost all the peak positions between the observed and simulated XRD results to identify the crystal structure of the synthesized material. In addition, the molar ratio of Mn : P in MnPi is 3 : 2.02 based on the EDX analysis. The temperature dependent magnetic susceptibility of MnPi indicates a high spin Mn(II) state (Fig. S10, ESI[†]).³⁸ These results indicate that the as-prepared MnPi is an analogue of the reported metaswitzerite with the same crystal structure. Thus, it is possible to illustrate the structure of the as-prepared Fe-free MnPi analogue based on the crystal structure of metaswitzerite. The simulated XRD pattern of the MnPi metaswitzerite structure (ICSD-100263) is shown in Fig. 2D (black line), demonstrating the structural consistency between the metaswitzerite and the as-prepared MnPi.

The crystal structure of the MnPi is illustrated in Fig. 2E and S11–S14 (ESI[†]). The following information can be concluded. First, six different Mn sites are determined. Second, 6-coordinated Mn(1), Mn(2), Mn(3), and Mn(4) octahedrons are connected to form a compact layer parallel to the (001) plane. In this layer, each Mn octahedron is surrounded by the other three different Mn octahedrons. On average, every Mn atom in this layer has two bridging water ligands, each of which connecting two Mn atoms *via* the $\mu_2\text{-O}_w$ bridge. Third, the 5-coordinated Mn(5) trigonal bipyramid and 6-coordinated Mn(6) octahedron, as out-of-plane Mn centres, form another layer parallel to the above-mentioned layer. Of particular note is that Mn(5) has one

terminal coordinated water molecule and Mn(6) has two terminal coordinated water molecules. These coordination sites with terminal water molecules are critical in water oxidation. The terminal water on Mn(5,6) can participate in water oxidation to form O₂. After the release of O₂, the coordination sites will be available for new water molecules. In addition, 5-coordinated Mn is widely reported in MnO_x materials as the active centre for water oxidation.¹⁶ In our MnPi, the Mn(5) trigonal bipyramid is highly distorted with one terminal water-coordination. This structure is essentially promising for water oxidation.¹⁷ The structures of the Mn coordination with Mn–O bond lengths are shown in Fig. S14 (ESI[†]). As can be seen, the Mn(6) has the lowest symmetry in terms of Mn–O bond lengths in the five 6-coordinated Mn atoms (Mn(1–4) and Mn(6)). Meanwhile, Mn(5) is 5-coordinated and should have the highest tolerance for the Mn^{III} distortion. The HRTEM image of the basal plane is shown in Fig. S15 (ESI[†]), indicating the lattice spacing of the (400) facet. Thus, the most exposed sites are either the Mn(1–4) layer or the parallel Mn(5,6) layer depending on the termination of the sheet along the *c*-axis. Considering the average thickness of the nanosheet at ~ 3.4 nm, one sheet contains around 4 Mn(1–4) layers plus 4 Mn(5,6) layers in tandem.

The electrocatalytic water oxidation performance of MnPi was evaluated in a 0.05 M phosphate buffer (pH = 7) by cyclic voltammetry (CV). As shown in Fig. 3A, the catalytic performance of

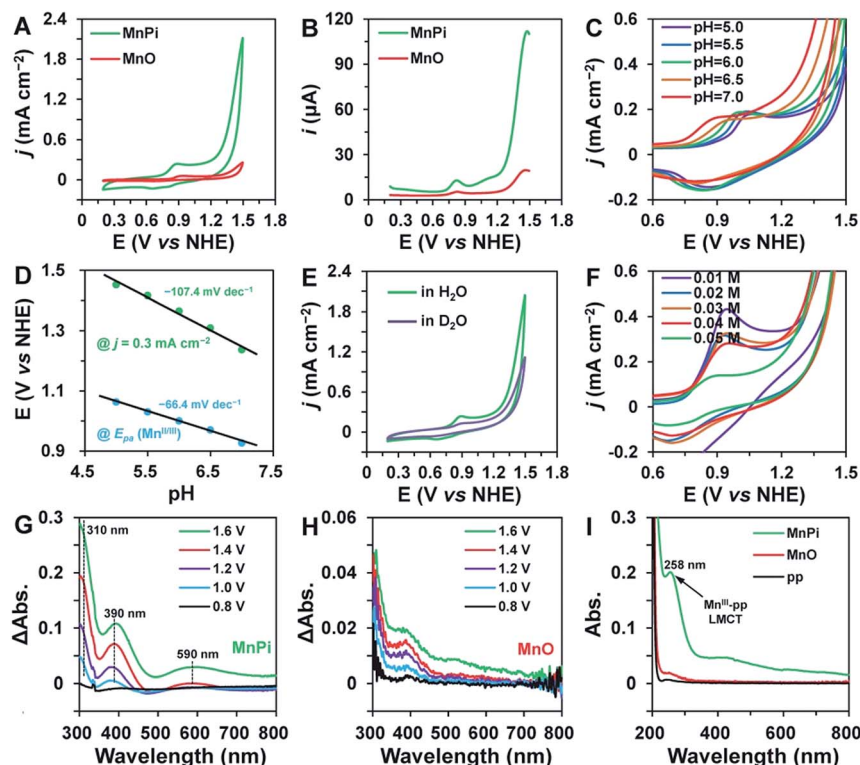


Fig. 3 (A) The CV and (B) DPV curves of the MnPi and MnO electrocatalysts. (C) The current and potential response of the MnPi electrocatalyst to the pH values of the electrolyte. (D) The plots of the potentials at $E_{pa}(\text{Mn}^{\text{II/III}})$ and $j = 0.3 \text{ mA cm}^{-2}$ against the pH values of the electrolyte. (E) The CV curves of the MnPi sample in H₂O and D₂O. (F) The current and potential response of the MnPi electrocatalyst to the concentration of phosphate anions. (G and H) The *in situ* UV-vis absorbance of the MnPi and MnO electrocatalysts under OER conditions at different applied potentials. The spectra at 0.5 V were used as the reference. (I) The UV-vis absorption spectra of the pyrophosphate (pp) solution after 2 h electrolysis with MnPi and MnO electrocatalysts.



MnP_i is much better than that of MnO, which has the same Mn valence. It requires an overpotential of 563 mV to reach an OER current density of 1 mA cm⁻² in a neutral aqueous solution on a glassy carbon electrode. This performance is among the top values reported in the literature for Mn-based OER electrocatalysts, as shown in Table S2 (ESI†).^{5,6,11,12,18} However, we have to note that some of these studies focus on the detailed mechanism studies rather than the optimization of OER activity. A remarkable quasi-reversible redox peak is detected with $E_{pa} = 0.9$ V *vs.* the normal hydrogen electrode (NHE, all potentials are *versus* NHE unless otherwise stated), which is assigned to the Mn^{II/III} couple.^{22,23} The reverse cathodic scan of the CV plot displays two consecutive reduction peaks, which are probably due to the two-step reduction of Mn^{IV} species to Mn^{II} or the reduction of two different Mn^{III} species to Mn^{II}. Differential pulse voltammetry (DPV) is adopted to gain more details of the precatalytic features (Fig. 3B). Of particular note is that an additional oxidation peak, which is absent in MnO, can be detected at around 1.12 V following the Mn^{II/III} oxidation of MnPi. As reported in the literature, the Mn^{III} state in Mn-based oxides is unstable under neutral conditions (due to the J-T distortion of the symmetric Mn^{III} coordination) by involving disproportionation into Mn^{II} and Mn^{IV}.²³ Thus, it is reasonable to observe the absence of the oxidation of Mn^{III} into higher valence states in MnO, which has a symmetric Mn coordination.³⁹ The stabilization of the Mn^{III} state and its consequent oxidation into higher states in MnPi is one of the reasons for the much improved catalytic activity, as compared with MnO. The OER is triggered by further oxidation at higher potentials after the second oxidation of MnPi. This further oxidation is generally recognized as the formation of active -Mn^V=O (formal oxidation states) species.^{4,40} In addition, the performance of MnPi is also much better than that of Mn-LNPs (Fig. S16, ESI†). The electrochemical surface areas (ECSA) of MnPi, Mn-LNPs and MnO are provided in Fig. S17 (ESI†). As expected, the MnPi has the highest ECSA. Taking into consideration the ECSA, the normalized activity is provided in Fig. S18 (ESI†), showing the highest intrinsic OER activity of MnPi as a result of the Mn geometry. In particular, the MnO does not contain asymmetric Mn centres and the Mn-LNPs does not contain coordinated water molecules.

The current-potential responses of i , i/ν and $i/\sqrt{\nu}$ are recorded to analyse the controlling processes of the pre-catalysis and catalysis in MnPi (Fig. S19, ESI†).⁴¹ The following information can be concluded. First, the quasi-reversible Mn^{II/III} redox couple becomes reversible at high scan rates (Fig. S19A, ESI†), indicating that the resting states can be fully regenerated after the completion of the catalytic cycle and the resting states are sensitive to its surroundings (electrolyte, oxygen, *etc.*). Second, the material displays semiconducting behaviour within the complete precatalytic potential range, which is consistent with the nature of transition metal phosphates. Third, the currents before the first oxidation ($i \propto \nu$ region, Fig. S19B, ESI†) are kinetic-controlled by double-layer capacitance (~ 30.9 μ F). After that, the currents are generally kinetic-controlled by diffusion ($i \propto \sqrt{\nu}$ region, Fig. S19C, ESI†), indicating that there is still room for increasing the structure voids in the layered MnPi toward higher performance.

To shed more light on the pre-catalysis and catalysis, the current responses to the nature of the buffer solutions are recorded under similar conditions (Fig. 3C-F). As shown in Fig. 3C, the Mn^{II/III} oxidation is dependent on the pH values of the electrolyte. The E_{pa} values have a linear relationship with pH values with a slope of -66.4 mV pH⁻¹, indicating a ne^-/nH^+ proton-coupled electron transfer (PCET) process (the theoretical value of such a process is -59 mV pH⁻¹).⁴² In detail, the Mn^{II/III} oxidation is associated with the removal of one proton from the coordinated water/hydroxyl. The phosphate anions and μ_2 -O_w in the material are beneficial for this oxidation process due to their proton-binding ability.⁴³ Meanwhile, the catalytic currents are also dependent on the pH values of the electrolyte. At a current density of 0.3 mA cm⁻², the required potential is proportional to the pH values with a linear slope of -107.4 mV pH⁻¹. In this catalytic region, the Tafel slope is determined to be 237.2 mV dec⁻¹ (Fig. S20, ESI†). An inverse reaction order close to 0.5 on proton activity is calculated based on eqn (S1) (ESI†). This value would result from the combination of two primary competing pathways of zeroth-order and inverse first-order [H⁺] dependence.⁴² Thus, the rate-determining step (rds) in the latter pathway may involve the nucleophilic attack on -Mn^V=O (formal oxidation states) by a water molecule (a proton is generated as the product).³ This hypothesis is further proved by the kinetic isotope effect (KIE) experiment (Fig. 3E). The OER rate is much slower in a D₂O solution, indicating that the removal of protons is involved in the rds.²¹ In addition, the current of the Mn^{II/III} oxidation also indicates a KIE, which is consistent with the abovementioned PCET feature of the oxidation. The Nyquist plot of MnPi derived from the electrochemical impedance spectroscopy is shown in Fig. S21 (ESI†), indicating a poor conductivity of the inorganic phosphate. The current dependence on phosphate concentration is shown in Fig. 3F. The results indicate that the E_{pa} position (Mn^{II/III}) and the catalytic current are independent of the buffer concentration. As compared with the results in electrolytes with lower concentrations, the E_{pa} of the sample recorded in 0.05 M phosphate buffer solution is affected by the capacitance or further oxidation events due to the diffusion limitation of the substances. The peak intensities are mainly affected by the background currents arising from different specific capacitances in buffer solutions of different concentrations. In some cases, lower concentrations of electrolyte can cause higher capacitances.⁴⁴ The role of phosphate anions in promoting the PCET process is demonstrated by the much higher Tafel slope in a NaClO₄ solution (Fig. S22, ESI†).⁴⁵

The stability of the MnPi catalyst was evaluated by controlled potential electrolysis (Fig. S23, ESI†), showing a stable OER current within 20 h. In contrast, the MnO sample displayed lower current density with inferior stability. The core X-ray photoelectron spectroscopy (XPS) spectra of the MnPi (green line), Mn-LNPs (purple line) and MnPi after electrolysis (blue line) are displayed in Fig. S24A-C (ESI†). The peak positions of the Mn spectra remained almost unchanged, indicating the structural stability of Mn coordination after sonication and electrolysis. The peak position of the Mn 2p_{3/2} (641–642 eV), the presence of the satellite peak of Mn 2p_{3/2} (~ 647 eV), and the



nanoplates for an efficient electrocatalytic OER in neutral aqueous solutions. Under controlled conditions, the sonication-derived nanosheets are not isolated but are unusually assembled to form a 3D superstructure. Thus, the material has both 2D and 3D features that are beneficial to electrocatalysis. From structural analysis, it is found that the material has six different Mn centres with phosphate anions and water molecules as the coordination ligands. Due to the asymmetric geometry of Mn centres, the J–T distortion of Mn^{III} can be tolerated and the key Mn^{III} active intermediate is thereby stabilized in MnPi, as demonstrated by the electrochemical and spectrometric studies. From kinetic analysis, it is found that the Mn^{II/III} oxidation and the rds of the OER (O–O bond formation) are proton-coupled processes. Thus, the presence of phosphate and aqua ligands is critical in the OER catalysis, assisting proton transfer and providing dissociative protons to lower the required activation energy of electron transfer. From computational studies, it is found that the out-of-plane 5-coordinated Mn(5) and 6-coordinated Mn(6) with terminal water ligands are preferential sites to be oxidized. These centres are believed to have superior activity because they can be oxidized to form active intermediates at lower potentials and can provide vacant coordination sites for the OER after the depletion of terminal water molecules. We believe that the reported convenient strategy to prepare a unique nanosheet assembly and the detailed study on the structure–performance relationship of MnPi will shed light on both practical and fundamental research of oxygen evolution chemistry.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We are grateful for the support from the National Natural Science Foundation of China under grant no. 21503126, 21573139, 21773146 and 21872092, the “Thousand Talents Program” of China, and the Starting Research Funds of Shaanxi Normal University.

Notes and references

- J. Qi, W. Zhang and R. Cao, *Adv. Energy Mater.*, 2018, **8**, 1701620.
- Y. Tachibana, L. Vayssieres and J. R. Durrant, *Nat. Photonics*, 2012, **6**, 511–518.
- W. Zhang, W. Lai and R. Cao, *Chem. Rev.*, 2017, **117**, 3717–3797.
- M. M. Najafpour, G. Renger, M. Holyńska, A. N. Moghaddam, E.-M. Aro, R. Carpentier, H. Nishihara, J. J. Eaton-Rye, J.-R. Shen and S. I. Allakhverdiev, *Chem. Rev.*, 2016, **116**, 2886–2936.
- W. Schöfberger, F. Faschinger, S. Chattopadhyay, S. Bhakta, B. Mondal, J. A. A. W. Elemans, S. Müllegger, S. Tebi, R. Koch, F. Klappenberger, M. Paszkiewicz, J. V. Barth, E. Rauls, H. Aldahhak, W. G. Schmidt and A. Dey, *Angew. Chem., Int. Ed.*, 2016, **55**, 2350–2355.
- A. Indra, P. W. Menezes, I. Zaharieva, E. Baktash, J. Pfrommer, M. Schwarze, H. Dau and M. Driess, *Angew. Chem., Int. Ed.*, 2013, **52**, 13206–13210.
- M. M. Najafpour, T. Ehrenberg, M. Wiechen and P. Kurz, *Angew. Chem., Int. Ed.*, 2010, **49**, 2233–2237.
- S. Lee, G. Nam, J. Sun, J.-S. Lee, H.-W. Lee, W. Chen, J. Cho and Y. Cui, *Angew. Chem., Int. Ed.*, 2016, **55**, 8599–8604.
- Y. Meng, W. Song, H. Huang, Z. Ren, S.-Y. Chen and S. L. Suib, *J. Am. Chem. Soc.*, 2014, **136**, 11452–11464.
- P. F. Smith, B. J. Deibert, S. Kaushik, G. Gardner, S. Hwang, H. Wang, J. F. Al-Sharab, E. Garfunkel, L. Fabris, J. Li and G. C. Dismukes, *ACS Catal.*, 2016, **6**, 2089–2099.
- A. Bergmann, I. Zaharieva, H. Dau and P. Strasser, *Energy Environ. Sci.*, 2013, **6**, 2745–2755.
- F. Zhou, A. Izgorodin, R. K. Hocking, L. Spiccia and D. R. MacFarlane, *Adv. Energy Mater.*, 2012, **2**, 1013–1021.
- C.-H. Kuo, W. Li, L. Pahalagedara, A. M. El-Sawy, D. Kriz, N. Genz, C. Guild, T. Ressler, S. L. Suib and J. He, *Angew. Chem., Int. Ed.*, 2015, **54**, 2345–2350.
- Y. Gorlin and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2010, **132**, 13612–13614.
- I. Zaharieva, P. Chernev, M. Risch, K. Klingan, M. Kohlhoff, A. Fischer and H. Dau, *Energy Environ. Sci.*, 2012, **5**, 7081–7089.
- G. Mattioli, I. Zaharieva, H. Dau and L. Guidoni, *J. Am. Chem. Soc.*, 2015, **137**, 10254–10267.
- B. Zhang, H. Chen, Q. Daniel, B. Philippe, F. Yu, M. Valvo, Y. Li, R. B. Ambre, P. Zhang, F. Li, H. k. Rensmo and L. Sun, *ACS Catal.*, 2017, **7**, 6311–6322.
- T. Takashima, K. Hashimoto and R. Nakamura, *J. Am. Chem. Soc.*, 2012, **134**, 1519–1527.
- Z. M. Chan, D. A. Kitchaev, J. N. Weker, C. Schnedermann, K. Lim, G. Ceder, W. Tumas, M. F. Toney and D. G. Nocera, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, E5261–E5268.
- J. Park, H. Kim, K. Jin, B. J. Lee, Y.-S. Park, H. Kim, I. Park, K. D. Yang, H.-Y. Jeong, J. Kim, K. T. Hong, H. W. Jang, K. Kang and K. T. Nam, *J. Am. Chem. Soc.*, 2014, **136**, 4201–4211.
- K. Jin, J. Park, J. Lee, K. D. Yang, G. K. Pradhan, U. Sim, D. Jeong, H. L. Jang, S. Park, D. Kim, N.-E. Sung, S. H. Kim, S. Han and K. T. Nam, *J. Am. Chem. Soc.*, 2014, **136**, 7435–7443.
- Y.-F. Li and Z.-P. Liu, *J. Am. Chem. Soc.*, 2018, **140**, 1783–1792.
- Q. Kang, L. Vernisse, R. C. Remsing, A. C. Thenuwara, S. L. Shumlas, I. G. McKendry, M. L. Klein, E. Borguet, M. J. Zdilla and D. R. Strongin, *J. Am. Chem. Soc.*, 2017, **139**, 1863–1870.
- A. C. Thenuwara, E. B. Cerkez, S. L. Shumlas, N. H. Attanayake, I. G. McKendry, L. Frazer, E. Borguet, Q. Kang, R. C. Remsing, M. L. Klein, M. J. Zdilla and D. R. Strongin, *Angew. Chem., Int. Ed.*, 2016, **55**, 10381–10385.
- F. Song and X. Hu, *Nat. Commun.*, 2014, **5**, 4477.
- C. Backes, T. M. Higgins, A. Kelly, C. Boland, A. Harvey, D. Hanlon and J. N. Coleman, *Chem. Mater.*, 2017, **29**, 243–255.



- 27 C. Tan, X. Cao, X.-J. Wu, Q. He, J. Yang, X. Zhang, J. Chen, W. Zhao, S. Han, G.-H. Nam, M. Sindoro and H. Zhang, *Chem. Rev.*, 2017, **117**, 6225–6331.
- 28 S. Chen, J. Duan, M. Jaroniec and S. Z. Qiao, *Angew. Chem., Int. Ed.*, 2013, **52**, 13567–13570.
- 29 Y. Yan, L. Thia, B. Y. Xia, X. Ge, Z. Liu, A. Fisher and X. Wang, *Adv. Sci.*, 2015, **2**, 1500120.
- 30 Y. Song, P. Y. Zavalij, N. A. Chernova and M. S. Whittingham, *Chem. Mater.*, 2003, **15**, 4968–4973.
- 31 B. Zhang, Y. Li, M. Valvo, L. Fan, Q. Daniel, P. Zhang, L. Wang and L. Sun, *ChemSusChem*, 2017, **10**, 4472–4478.
- 32 A. Indra, U. Paik and T. Song, *Angew. Chem., Int. Ed.*, 2018, **57**, 1241–1245.
- 33 Y. Zhao, C. Chang, F. Teng, Y. Zhao, G. Chen, R. Shi, G. I. N. Waterhouse, W. Huang and T. Zhang, *Adv. Energy Mater.*, 2017, **7**, 1700005.
- 34 J. Wang, H.-X. Zhong, Y.-L. Qin and X.-B. Zhang, *Angew. Chem., Int. Ed.*, 2013, **52**, 5248–5253.
- 35 R. Liu, Y. Wang, D. Liu, Y. Zou and S. Wang, *Adv. Mater.*, 2017, **29**, 1701546.
- 36 H.-R. Zhao, C. Xue, C.-P. Li, K.-M. Zhang, H.-B. Luo, S.-X. Liu and X.-M. Ren, *Inorg. Chem.*, 2016, **55**, 8971–8975.
- 37 L. Fanfani and P. F. Zanazzi, *TMPM, Tscherms Mineral. Petrogr. Mitt.*, 1979, **26**, 255–269.
- 38 O. S. Volkova, L. V. Shvanskaya, E. A. Ovchenkov, E. A. Zvereva, A. S. Volkov, D. A. Chareev, K. Molla, B. Rahaman, T. Saha-Dasgupta and A. N. Vasiliev, *Inorg. Chem.*, 2016, **55**, 10692–10700.
- 39 K. Jin, H. Seo, T. Hayashi, M. Balamurugan, D. Jeong, Y. K. Go, J. S. Hong, K. H. Cho, H. Kakizaki, N. g. Bonnet-Mercier, M. G. Kim, S. H. Kim, R. Nakamura and K. T. Nam, *J. Am. Chem. Soc.*, 2017, **139**, 2277–2285.
- 40 V. Krewald, M. Retegan, N. Cox, J. Messinger, W. Lubitz, S. DeBeer, F. Neese and D. A. Pantazis, *Chem. Sci.*, 2015, **6**, 1676–1695.
- 41 S. Wan, J. Qi, W. Zhang, W. Wang, S. Zhang, K. Liu, H. Zheng, J. Sun, S. Wang and R. Cao, *Adv. Mater.*, 2017, **29**, 1700286.
- 42 H. Michael, D. K. Bediako and D. G. Nocera, *J. Am. Chem. Soc.*, 2014, **136**, 6002–6010.
- 43 D. González-Flores, I. Sánchez, I. Zaharieva, K. Klingan, J. Heidkamp, P. Chernev, P. W. Menezes, M. Driess, H. Dau and M. L. Montero, *Angew. Chem., Int. Ed.*, 2015, **54**, 2472–2476.
- 44 C. C. L. McCrory, S. Jung, J. C. Peters and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2013, **135**, 16977–16987.
- 45 Y. Surendranath, M. W. Kanan and D. G. Nocera, *J. Am. Chem. Soc.*, 2010, **132**, 16501–16509.
- 46 C. Walter, P. W. Menezes, S. Orthmann, J. Schuch, P. Connor, B. Kaiser, M. Lerch and M. Driess, *Angew. Chem., Int. Ed.*, 2018, **57**, 698–702.
- 47 J. F. Moulder, W. F. Stickle, P. E. Sobol and K. D. Bomben, *Handbook of X-Ray Photoelectron Spectroscopy*, Perkin-Elmer, MN, USA, 1992.
- 48 Y. Gorlin, B. Lassalle-Kaiser, J. D. Benck, S. Gul, S. M. Webb, V. K. Yachandra, J. Yano and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2013, **135**, 8525–8534.
- 49 H. Simchi, K. A. Cooley, J. Ohms, L. Huang, P. Kurz and S. E. Mohny, *Inorg. Chem.*, 2018, **57**, 785–792.
- 50 T. Takashima, K. Hashimoto and R. Nakamura, *J. Am. Chem. Soc.*, 2012, **134**, 18153–18156.
- 51 A. Yamaguchi, R. Inuzuka, T. Takashima, T. Hayashi, K. Hashimoto and R. Nakamura, *Nat. Commun.*, 2014, **5**, 4256.
- 52 O. Diaz-Morales, D. Ferrus-Suspedra and M. T. M. Koper, *Chem. Sci.*, 2016, **7**, 2639–2645.

