

Cite this: *Dalton Trans.*, 2021, **50**,  
16133Received 2nd September 2021,  
Accepted 12th October 2021

DOI: 10.1039/d1dt02966e

rsc.li/dalton

## Atomic/molecular layer deposition of Ni-terephthalate thin films†

Anish Philip,<sup>a</sup> Sami Vasala,<sup>b</sup> Pieter Glatzel<sup>b</sup> and Maarit Karppinen<sup>\*a</sup>

Atomic/molecular layer deposition (ALD/MLD) is currently strongly emerging as an intriguing route for novel metal–organic thin-film materials. This approach already covers a variety of metal and organic components, and potential applications related to *e.g.* sustainable energy technologies. Among the 3d metal components, nickel has remained unexplored so far. Here we report a robust and efficient ALD/MLD process for the growth of high-quality nickel terephthalate thin films. The films are deposited from Ni(thd)<sub>2</sub> (thd: 2,2,6,6-tetramethyl-3,5-heptanedionate) and terephthalic acid (1,4-benzenedicarboxylic acid) precursors in the temperature range of 180–280 °C, with appreciably high growth rates up to 2.3 Å per cycle at 200 °C. The films are amorphous but the local structure and chemical state of the films are addressed based on XRR, FTIR and RIXS techniques.

### Introduction

Hybrid metal–organic materials have attracted widespread attention as they form a promising platform for realizing unprecedented combinations of chemical and physical properties that are often difficult if not impossible to achieve with conventional materials. Atomic/molecular layer deposition (ALD/MLD) technique provides us with a scientifically elegant yet industrially feasible way to fabricate these materials in high-quality thin-film form.<sup>1–4</sup> The method derives from the firmly established ALD (atomic layer deposition) technology for inorganic thin films, in which the atomic-level control of film thickness, composition and homogeneity stems from the self-limited gas–surface reactions of sequentially pulsed gaseous/evaporated inorganic precursors.<sup>5,6</sup> For example, in one of the prototype ALD processes, Al<sub>2</sub>O<sub>3</sub> thin films are grown from Al(CH<sub>3</sub>)<sub>3</sub> and H<sub>2</sub>O precursors. In a parallel technique for purely organic thin films, *i.e.* MLD (molecular layer deposition), two mutually reactive organic precursors are used.<sup>7</sup> In the combined ALD/MLD technique for the hybrid metal–organic films, the metal-entailing ALD precursor is combined with an organic MLD precursor.<sup>3,4</sup> Moreover, the ALD/MLD approach allows any arbitrary combinations of the ALD and MLD pulses such that *e.g.* ultrathin (monomolecular) organic layers can be introduced between thicker inorganic layers (grown with mul-

tipled ALD cycles) into various regular (superlattice) or irregular (gradient) multilayer structures.<sup>8–12</sup>

Facile ALD/MLD processes have already been developed for a rapidly expanding variety of different metal (*s*-block, *p*-block, *d*-block, lanthanide), and organic (allyl, aryl, pyridine, *etc.*) constituents.<sup>3,13–17</sup> Transition metal based hybrids and in particular those involving the late 3d metals with partially filled *d* orbitals are particularly intriguing candidates for magnetically, electrically, optically or catalytically active materials. So far – among the late 3d metals – well-behaving ALD/MLD processes have been developed for Mn, Fe, Co and Cu (see Table 1),<sup>18–23</sup> while for Ni very little efforts have been made. In previous literature, ultra-thin Ni<sub>4</sub>MP interfacial layers were grown for solar cell application from bis(dimethylamino-2-methyl-2-butoxy) nickel and 4-mercapto phenol precursors,<sup>11</sup> but no ALD process optimization details were reported.

Here our goal is to fill the gap within the late 3d transition metal based ALD/MLD processes. Besides the solar cell application,<sup>24</sup> Ni-organic thin films could be interesting for other emerging energy applications, *e.g.* supercapacitors.<sup>25–27</sup> Moreover, a facile ALD/MLD process for Ni-organics would be interesting also in the sense that it could be then combined with any of the already known ALD processes for NiO films for the fabrication of various layer-engineered NiO:organic multilayer structures. Nickel oxide as such is a wide bandgap *p*-type semiconductor, extensively investigated for applications such as resistive memories (memristors)<sup>28</sup> and photovoltaics.<sup>29</sup> For the ALD of NiO thin films, the most common nickel precursors are Ni(thd)<sub>2</sub> (thd: 2,2,6,6-tetramethyl-3,5-heptanedionate),<sup>30,31</sup> Ni(acac)<sub>2</sub> (acac: acetylacetonate),<sup>32</sup> and Ni(Cp)<sub>2</sub> (Cp: cyclopentadienyl).<sup>33</sup> Here we use Ni(thd)<sub>2</sub> as the nickel precursor, as it is stable enough to allow easy handling but has shown to be

<sup>a</sup>Department of Chemistry and Materials Science, Aalto University, P.O. Box 16100, FI-00076 Espoo, Finland. E-mail: maarit.karppinen@aalto.fi

<sup>b</sup>ESRF – The European Synchrotron, 71 Avenue des Martyrs, 38000 Grenoble, France

†Electronic supplementary information (ESI) available. See DOI: 10.1039/d1dt02966e



**Table 1** Summary of reported ALD/MLD processes for hybrid metal–organic thin films based on 3d transition metals

Metal	Metal precursor	Organic precursor	Deposition Temp (°C)	GPC (Å per cycle), *mass gain (ng cm <sup>-2</sup> )	Ref.
Titanium	TTIP	HQ	300	2.5	35
		TiCl <sub>4</sub>	GL	210	2.1
		GL	130	2.8	36
		EG	95–115	4.5	36
		EG	135	1.5	36
		4-AP	120–160	10–11	37
		ODA	160	0.3	38
		ODA	490	1.1	38
	Vanadium	VOCl <sub>3</sub>	EG	90–135	*15.2
V(CO) <sub>6</sub>		TCNE	RT	9.8	40
Manganese	Mn(thd) <sub>3</sub>	TPA	160–280	≈1.0	18
	Mn(CpEt) <sub>2</sub>	EG	160	0.9	20
Iron	FeCl <sub>3</sub>	TPA	240–260	11	23
		ADA	280	25	22
	Cp <sub>2</sub> Fe <sub>2</sub> (CO) <sub>4</sub>	HQ	180	≈3.7	41
		TPA	160–280	1.0–1.2	18
Cobalt	Co(acac) <sub>3</sub>	TPA	160–280	1.5	18
	Co(thd) <sub>2</sub>	4MP	180	2.26	11
Nickel	Ni(dmamb) <sub>2</sub>	TPA	180–280	0.7	19
Copper	Cu(thd) <sub>2</sub>	TPA	180–280	1.0–2.6	21
	Cu(dmap) <sub>2</sub>	HQ, TPA, ODA, PPD, BDT	120–240		

Abbreviations: Metal precursor/ligand; TTIP (titanium isopropoxide), thd (2,2,6,6-tetramethyl-3,5-heptanedionate), Cp (cyclopentadienyl), CpEt (ethylcyclopentadienyl), acac (acetylacetonate), dmamb (dimethylamino-2-methyl-2-butoxo), dmap (dimethyl aminopropoxide). Organic precursor: HQ (hydroquinone), GL (glycerol), EG (ethylene glycol), 4-AP (4-aminophenol), ODA (4,4'-oxydianiline), TCNE (tetracyanoethylene), TPA (terephthalic acid), ADA (azobenzenedicarboxylic acid), MP (mercapto phenol), PPD (*p*-phenylenediamine), BDT (1,4-benzenedithiol).

reactive enough to yield NiO films even at relatively low temperatures.<sup>30,31</sup> Of the possible organic precursors, we chose terephthalic acid (TPA; 1,4-benzenedicarboxylic acid) as it is known to be reactive enough towards the thd-based metal-bearing precursors.<sup>19,34</sup> Another motivation for the use of TPA is the fact that it has shown to form metal–organic framework (MOF) structured materials with Ni in bulk form.<sup>26</sup> Moreover, the combination, Ni(thd)<sub>2</sub> + TPA, allows the straightforward comparison with the similar processes for Mn, Co and Cu.<sup>19,34</sup> For molecular structures of the precursors, see Fig. 1.

## Experimental


The Ni-TPA films were grown from the following precursors: in-house synthesized Ni(thd)<sub>2</sub> (thd = 2,2,6,6-tetramethyl-3,5-heptanedione) and commercial TPA (benzene-1,4-dicarboxylic acid; Tokyo Chemical Industry Co. Ltd). These precursor powders were placed in open boats inside the reactor (flow-type hot-wall ALD reactor; F-120 by ASM Microchemistry Ltd)

and heated for evaporation at 115 and 180 °C, respectively, based on our previous experience on these precursors in other processes.<sup>12,42</sup> Nitrogen (>99.999%, Schmidlin UHPN 3000 N<sub>2</sub> generator) was used as a carrier and purging gas, and the pressure inside the reactor was 3–4 mbar. The precursor pulse lengths and the deposition (substrate heating) temperature were optimized in the study. The depositions were performed on Si(100) substrates.

The success of the film growth was routinely evaluated using X-ray reflectivity measurements (XRR; X'Pert MPD PRO Alfa 1, PANalytical, Cu K<sub>α</sub>). The XRR patterns were fitted by X'Pert Reflectivity software by PANalytical for the film thickness, density and roughness, and the so-called growth-per-cycle (GPC) value was calculated by dividing the film thickness by the number of deposition cycles applied. The density ( $\rho_e$ ) values were calculated from the critical angle ( $\theta_c$ ) as follows:  $\rho_e = (\theta_c^2 \pi) / (\lambda^2 r_e)$ , where  $\lambda$  is the X-ray wavelength and  $r_e$  is the classical electron radius. Crystallinity of the films was investigated by grazing-incidence X-ray diffraction (GIXRD; incident angle 0.5°) using the same equipment.

To address the bonding structure/local symmetry/chemical state of the films, both Fourier transform infrared (FTIR; Bruker alpha II) and resonant inelastic X-ray scattering (RIXS) experiments were carried out. The FTIR measurements were carried out in a transmission mode in the range of 400–4000 cm<sup>-1</sup> with a resolution of 4 cm<sup>-1</sup>; each given spectrum is an average of 24 measured spectra, from which a spectrum of blank Si is subtracted.

The Ni 1s2p RIXS planes were measured at beamline ID26 of the European Synchrotron Radiation Facility in Grenoble, France. Third harmonic of the undulator source was used and

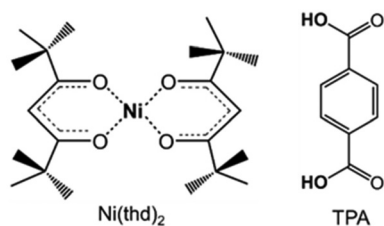

**Fig. 1** Molecular structures of the precursors employed in this study.





The Ni-TPA films were found amorphous from GIXRD investigation independent of the deposition temperature used. Also, the SEM imaging revealed no macroscopic grains for these films (data not shown here). However, an interesting observation was made from the XRR data from which we estimated the film density to be *ca.*  $1.4 \text{ g cm}^{-3}$  with a very weak increasing trend upon increasing the deposition temperature from 180 to 280 °C. This density value is somewhat low compared to those ( $1.6\text{--}1.9 \text{ g cm}^{-3}$ ) observed for the amorphous Mn-TPA and Co-TPA films earlier.<sup>18</sup> Then, differently from the Mn-, Co- and Ni-based processes, the Cu(thd)<sub>2</sub> + TPA process yielded amorphous films with densities of  $2 \text{ g cm}^{-3}$  or higher only at deposition temperatures higher than 200 °C, but crys-

talline (MOF-2 structured) Cu-TPA films with a density of *ca.*  $1.4 \text{ g cm}^{-3}$  in the lowest deposition temperature range of 180–190 °C.<sup>19</sup> Reflecting against these previous results, we hypothesize that the present Ni-TPA films with the low densities similar to those of the crystalline Cu-TPA films could be crystalline in nanoscale. To challenge the possibility to obtain GIXRD-crystalline Ni-TPA films, we carried out additional test depositions at the “non-ideally” low deposition temperature of 170 °C (lower than the evaporation temperature of the TPA precursor); however, no sign of crystallinity was seen in the GIXRD patterns for these thin films either.

To address the bonding/local structures in the Ni-TPA films, we carried out both FTIR and RIXS experiments. In Fig. 3, FTIR spectra for a series of Ni-TPA films deposited at different temperatures are shown. In these spectra, the decreasing peak intensity with increasing deposition temperature is simply due to the lower film thicknesses of the samples deposited at the higher temperatures (as all samples were deposited using the same number of ALD/MLD cycles, and the growth rate decreased with increasing deposition temperature). Otherwise, the spectra do not show any clear differences, confirming that the local bonding structures in the films are essentially independent of the deposition temperature. Also, they are quite similar to other previously reported metal-TPA spectra.<sup>23,34,53</sup> The fact that the spectra are essentially free of the characteristic features of hydroxy groups in the 1700–3500  $\text{cm}^{-1}$  range confirms that the films do not contain any coordinated water, and also that the carboxylic acid groups of the terephthalic acid precursor have completely bonded to the Ni atoms, as expected. The characteristic C–H vibration of the benzene ring is observed at 750  $\text{cm}^{-1}$ , but the most indicative part of the spectra is the range from 1300 to 1600  $\text{cm}^{-1}$  where the strong symmetric ( $\nu_s$ ) and asymmetric ( $\nu_{as}$ ) stretching bands of the carboxylate group are seen. For our Ni-TPA films these bands peak at *ca.* 1383 and 1571  $\text{cm}^{-1}$ , respectively. The separation between these peaks, *i.e.*  $\Delta = \nu_{as} -$

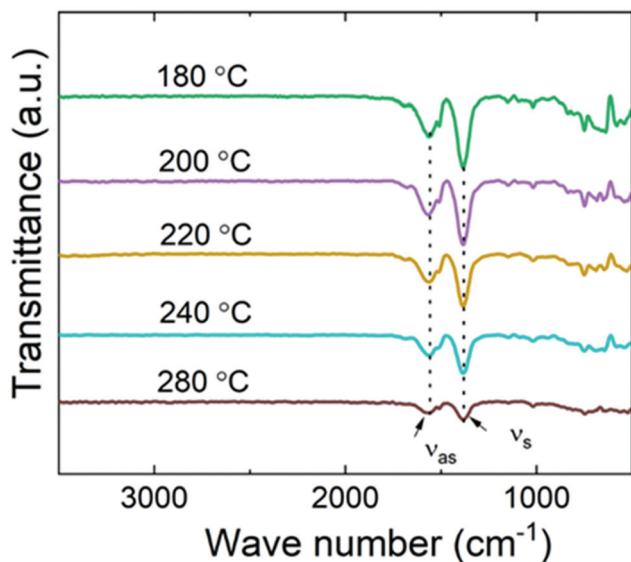


Fig. 3 FTIR spectra for Ni-TPA films deposited at different temperatures.

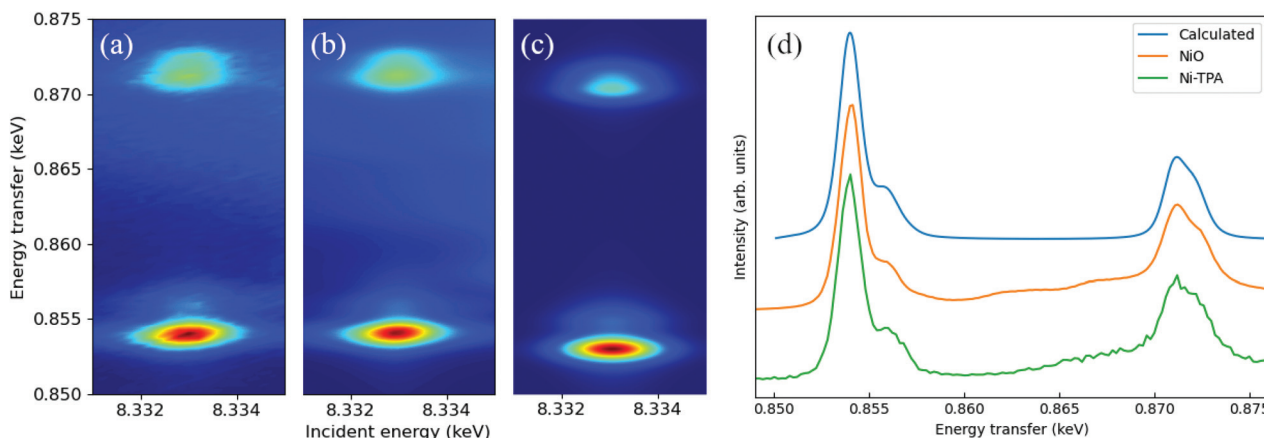


Fig. 4 (a) Measured Ni-TPA 1s2p RIXS plane, (b) measured NiO 1s2p RIXS plane, (c) calculated 1s2p RIXS plane for Ni<sup>2+</sup> in octahedral (O<sub>h</sub>) symmetry, and (d) constant incident energy cuts for Ni-TPA, NiO and the calculated RIXS planes at 8.333 keV incident energy. The calculated spectrum in (d) was shifted up in energy by 1.1 eV.



$\nu_s$ , provides us information of the bonding mode; here for Ni-TPA the  $\Delta = 188 \text{ cm}^{-1}$  value falls between  $130 < \Delta < 200$ , which is a clear indication of the bridging-type bonding,<sup>23,54</sup> similarly to the Mn-TPA, Co-TPA and Cu-TPA cases.<sup>18,19</sup>

The measured Ni-TPA 1s2p RIXS plane is shown in Fig. 4a. In addition, Fig. 4b shows the corresponding RIXS plane for the NiO reference and Fig. 4c a simulated RIXS plane for Ni<sup>2+</sup> in octahedral ( $O_h$ ) coordination. There is a good qualitative match between the experimental and calculated spectra; calculations with tetrahedral ( $T_d$ ) or other non-octahedral symmetries did not result in such good matches. Fig. 4d shows a constant incident energy (CIE) cut of the Ni-TPA RIXS plane at 8.333 keV, together with the same cuts of for NiO and the calculated RIXS plane. The calculated spectrum was shifted up by 1.1 eV to match the position of the experimental spectra. The best fit between the calculated CIE cut and the experimental results was found with a crystal field splitting of  $10D_q = 1.4 \text{ eV}$ . However, a closer inspection of the measured RIXS planes revealed a tiny distortion from the ideal octahedral symmetry for both Ni-TPA and NiO (see ESI†). At room temperature, the NiO structure is known to be slightly distorted due to antiferromagnetic ordering, resulting in the Ni–O bond angles to deviate from the ideal  $90^\circ$  by a fraction of a degree ( $0.07^\circ$  or less).<sup>55,56</sup> The similarity between the Ni-TPA and NiO RIXS planes indicate a similar tiny distortion from octahedral symmetry also in case of the Ni-TPA. These results indicate that the nickel in Ni-TPA is divalent and in an almost ideal octahedral coordination. Thus, based on the RIXS and FTIR analyses, showing octahedral coordination around the Ni atoms with bridging-type bonding of the surrounding terephthalate groups, we imagine that our Ni-TPA films grow as sketched in Fig. 5.

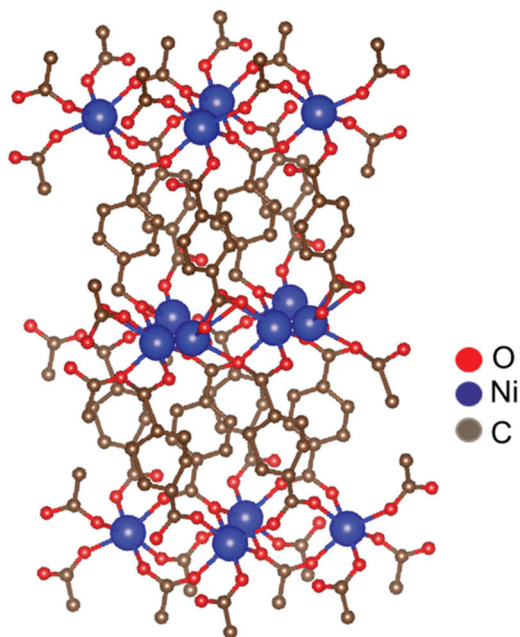


Fig. 5 Schematic illustration of the (bonding) structure of Ni-TPA films.

## Conclusions

In this work, we have filled the gap in ALD/MLD processes for the series of 3d transition-metal based metal–organic thin films. Our Ni-TPA films deposited from Ni(thd)<sub>2</sub> and terephthalic acid precursors in the temperature range from 180 to 280 °C were amorphous according to GIXRD but the significantly low-density values determined with XRR suggested some local ordering indicative of a porous structure.

The films grew with an appreciably high growth rate, which decreased from the value of 3.0 Å per cycle at 180 °C with increasing deposition temperature, in a fashion typical for the related Mn-TPA, Co-TPA and Cu-TPA films and also for many other ALD/MLD metal–organic thin films.

Since our Ni-TPA films were amorphous in GIXRD, we addressed the bonding/local structures using FTIR and synchrotron-based RIXS techniques, the latter experiments been so far rarely exploited for similar thin film systems. We could conclude that the terephthalate groups bond to divalent nickel ions in a bridging-type fashion to form (slightly distorted) octahedral coordination spheres around them.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

We acknowledge the funding from Academy of Finland (Profi 3), and the use of the RawMatTERS Finland Infrastructure (RAMI) at Aalto University. The measured data of RIXS will be available for public after three years period following DOI: 10.15151/ESRF-ES-438677278.

## Notes and references

- 1 Y. Zhao, L. Zhang, J. Liu, K. Adair, F. Zhao, Y. Sun, T. Wu, X. Bi, K. Amine, J. Lu and X. Sun, *Chem. Soc. Rev.*, 2021, **50**, 3889–3956.
- 2 X. Meng, *J. Mater. Chem. A*, 2017, **5**, 18326–18378.
- 3 P. Sundberg and M. Karppinen, *Beilstein J. Nanotechnol.*, 2014, **5**, 1104–1136.
- 4 S. M. George, B. Yoon and A. A. Dameron, *Acc. Chem. Res.*, 2009, **42**, 498–508.
- 5 R. W. Johnson, A. Hultqvist and S. F. Bent, *Mater. Today*, 2014, **17**, 236–246.
- 6 M. Leskelä, M. Mattinen and M. Ritala, *J. Vac. Sci. Technol., B*, 2019, **37**, 030801.
- 7 T. Yoshimura, S. Tatsuura and W. Sotoyama, *Appl. Phys. Lett.*, 1991, **59**, 482–484.
- 8 K. H. Yoon, K. S. Han and M. M. Sung, *Nanoscale Res. Lett.*, 2012, **7**, 71.



- 9 T. Tynell, A. Giri, J. Gaskins, P. E. Hopkins, P. Mele, K. Miyazaki and M. Karppinen, *J. Mater. Chem. A*, 2014, **2**, 12150–12152.
- 10 F. Krahl, A. Giri, J. A. Tomko, T. Tynell, P. E. Hopkins and M. Karppinen, *Adv. Mater. Interfaces*, 2018, **5**, 1701692.
- 11 L. Lee, J. Park, K. S. Han, R. S. Kumar and M. M. Sung, *Appl. Surf. Sci.*, 2019, **476**, 897–904.
- 12 A. Philip, J. P. Niemelä, G. C. Tewari, B. Putz, T. E. J. Edwards, M. Itoh, I. Utke and M. Karppinen, *ACS Appl. Mater. Interfaces*, 2020, **12**, 21912–21921.
- 13 H. Zhu, M. H. Aboonassr Shiraz, L. Yao, K. Adair, Z. Wang, H. Tong, X. Song, T. K. Sham, M. Arjmand, X. Song and J. Liu, *Chem. Commun.*, 2020, **56**, 13221–13224.
- 14 J. Penttinen, M. Nisula and M. Karppinen, *Chem. – Eur. J.*, 2017, **23**, 18225–18231.
- 15 C. MacIsaac, J. R. Schneider, R. G. Closser, T. R. Hellstern, D. S. Bergsman, J. Park, Y. Liu, R. Sinclair and S. F. Bent, *Adv. Funct. Mater.*, 2018, **28**, 1800852.
- 16 K. B. Lausund, M. S. Olsen, P. A. Hansen, H. Valen and O. Nilsen, *J. Mater. Chem. A*, 2020, **8**, 2539–2548.
- 17 Z. Giedraityte, M. Tuomisto, M. Lastusaari and M. Karppinen, *ACS Appl. Mater. Interfaces*, 2018, **10**, 8845–8852.
- 18 E. Ahvenniemi and M. Karppinen, *Dalton Trans.*, 2016, **45**, 10730–10735.
- 19 E. Ahvenniemi and M. Karppinen, *Chem. Commun.*, 2016, **52**, 1139–1142.
- 20 D. S. Bergsman, J. G. Baker, R. G. Closser, C. MacIsaac, M. Lillethorup, A. L. Strickler, L. Azarnouche, L. Godet and S. F. Bent, *Adv. Funct. Mater.*, 2019, **29**, 1904129.
- 21 D. J. Hagen, L. Mai, A. Devi, J. Sainio and M. Karppinen, *Dalton Trans.*, 2018, **47**, 15791–15800.
- 22 A. Khayyami, A. Philip and M. Karppinen, *Angew. Chem., Int. Ed.*, 2019, **58**, 13400–13404.
- 23 A. Tanskanen and M. Karppinen, *Sci. Rep.*, 2018, **8**, 8976.
- 24 F. Ran, X. Xu, D. Pan, Y. Liu, Y. Bai and L. Shao, *Nano-Micro Lett.*, 2020, **12**, 46.
- 25 D. Sheberla, J. C. Bachman, J. S. Elias, C. J. Sun, Y. Shao-Horn and M. Dincă, *Nat. Mater.*, 2017, **16**, 220–224.
- 26 T. Deng, X. Shi, W. Zhang, Z. Wang and W. Zheng, *iScience*, 2020, **23**, 101220.
- 27 Y. Qu, C. Shi, H. Cao and Y. Wang, *Mater. Lett.*, 2020, **280**, 128526.
- 28 D. Ielmini, F. Nardi and C. Cagli, *Nanotechnology*, 2011, **22**, 254022.
- 29 J. W. Jung, C. C. Chueh and A. K. Y. Jen, *Adv. Mater.*, 2015, **27**, 7874–7880.
- 30 E. Lindahl, J. Lu, M. Ottosson and J. O. Carlsson, *J. Cryst. Growth*, 2009, **311**, 4082–4088.
- 31 E. Lindahl, M. Ottosson and J. O. Carlsson, *Chem. Vap. Deposition*, 2009, **15**, 186–191.
- 32 M. Utriainen, M. Kröger-Laukkanen and L. Niinistö, *Mater. Sci. Eng., B*, 1998, **B54**, 98–103.
- 33 J. Chae, H. S. Park and S. W. Kang, *Electrochem. Solid-State Lett.*, 2002, **5**, 64–66.
- 34 E. Ahvenniemi and M. Karppinen, *Chem. Mater.*, 2016, **28**, 6260–6265.
- 35 A. Philip, R. Ghiyasi and M. Karppinen, *ChemNanoMat*, 2021, **7**, 253–256.
- 36 A. I. Abdulagatov, R. A. Hall, J. L. Sutherland, B. H. Lee, A. S. Cavanagh and S. M. George, *Chem. Mater.*, 2012, **24**, 2854–2863.
- 37 P. Sundberg and M. Karppinen, *Eur. J. Inorg. Chem.*, 2014, **2014**, 968–974.
- 38 A. Sood, P. Sundberg, J. Malm and M. Karppinen, *Appl. Surf. Sci.*, 2011, **257**, 6435–6439.
- 39 A. I. Abdulagatov, K. N. Ashurbekova, K. N. Ashurbekova, R. R. Amashaev, M. K. Rabadanov and I. M. Abdulagatov, *Russ. J. Appl. Chem.*, 2018, **91**, 347–359.
- 40 C. Y. Kao, J. W. Yoo, Y. Min and A. J. Epstein, *ACS Appl. Mater. Interfaces*, 2012, **4**, 137–141.
- 41 A. Tanskanen and M. Karppinen, *Dalton Trans.*, 2015, **44**, 19194–19199.
- 42 D. J. Hagen, T. S. Tripathi, I. Terasaki and M. Karppinen, *Semicond. Sci. Technol.*, 2018, **33**, 115015.
- 43 P. Glatzel, A. Harris, P. Marion, M. Sikora, T. C. Weng, C. Guilloud, S. Lafuerza, M. Rovezzi, B. Detlefs and L. Ducotté, *J. Synchrotron Radiat.*, 2021, **28**, 362–371.
- 44 S. Lafuerza, M. Retegan, B. Detlefs, R. Chatterjee, V. Yachandra, J. Yano and P. Glatzel, *Nanoscale*, 2020, **12**, 16270–16284.
- 45 M. W. Haverkort, M. Zwierzycki and O. K. Andersen, *Phys. Rev. B*, 2012, **85**, 165113.
- 46 M. Retegan, *Zenodo*, DOI: 10.5281/zenodo.1008184.
- 47 J. Multia, A. Khayyami, J. Heiska and M. Karppinen, *J. Vac. Sci. Technol., A*, 2020, **38**, 052406.
- 48 J. Multia, J. Heiska, A. Khayyami and M. Karppinen, *ACS Appl. Mater. Interfaces*, 2020, **12**, 41557–41566.
- 49 B. H. Lee, B. Yoon, A. I. Abdulagatov, R. A. Hall and S. M. George, *Adv. Funct. Mater.*, 2013, **23**, 532–546.
- 50 Y. Du and S. M. George, *J. Phys. Chem. C*, 2007, **111**, 8509–8517.
- 51 R. L. Puurunen, *J. Appl. Phys.*, 2005, **97**, 121301.
- 52 M. Ylilammi, *Thin Solid Films*, 1996, **279**, 124–130.
- 53 L. Ai, C. Zhang, L. Li and J. Jiang, *Appl. Catal., B*, 2014, **148–149**, 191–200.
- 54 K. B. Klepper, O. Nilsen, S. Francis and H. Fjellvåg, *Dalton Trans.*, 2014, **43**, 3492–3500.
- 55 N. C. Tombs and H. P. Rooksby, *Nature*, 1950, **165**, 442–443.
- 56 D. Rodic, V. Spasojevic, V. Kusigerski, R. Tellgren and H. Rundlof, *Phys. Status Solidi B*, 2000, **218**, 527–536.

