



Cite this: *Mater. Adv.*, 2021,
2, 4859

Asymmetric D–A–D' Scaffold inducing distinct mechanochromic luminescence†

Huifang Yang,^a Zhiyuan Fu,^b Sai Wang,^a Haichao Liu,^c Jianwei Zhou,^a
Kai Wang,^{id}*^b Xiugang Wu,^{*a} Bing Yang,^{id}^c Bo Zou^{id}^b and Weiguo Zhu^{id}*^a

Mechanochromic luminescence (MCL) materials have a high requirement in high-tech applications such as pressure sensors and data storage. Nevertheless, the diversity of these emitters is rather restricted owing to the lack of clear molecular structure design guidelines, and it is imperative to develop creative multi-stimulus responsive compounds with polychromatic emission under different types of mechanical forces. In order to overcome difficulties of a single molecule exhibiting obvious MCL responses towards mechanical forces, in this study, a powerful approach of distinct multi-stimulus responsive MCL materials is to integrate the distinguished ability of donor units (D'), i.e. stronger phenothiazine (PTZ) and weaker bis(4-(*tert*-butyl)phenyl)amine (tDPA) compared with 9H-carbazole, directly into the same donor–acceptor (D–A) scaffold of 2-(4-(carbazol-9-yl)phenyl)-isoindoline-1,3-dione (CzPL) and hence obtaining **CzPL-PTZ** and **CzPL-tDPA**. Distinct MCL were primarily found for the parent **CzPL-PTZ** and **CzPL-tDPA** crystals under tensile force, and anisotropic and isotropic pressures. Interestingly, both crystals show an abnormal blue-shifted emission under crushing force. When under anisotropic pressure, the **CzPL-PTZ** ground sample further displays blue-shifted emission, but the **CzPL-tDPA** ground sample displays red-shifted emission. In contrast, both parent crystals show a similarly red-shifted and weakened emission under increasing isotropic pressure. Furthermore, these emissions exhibit a linear relationship between wavelength and pressure. More importantly, crystal **CzPL-PTZ** can completely return to the initial state once decompressed due to the reversible 3D short-range intermolecular interaction network; in contrast, the crystal **CzPL-tDPA** cannot fully recover to its original state after removing pressure due to the lattice vibration under a high pressure. The interesting and distinct MCL behaviors of **CzPL-PTZ** and **CzPL-tDPA** indicate that the D–A–D' molecular design should provide pragmatic insights towards MCL materials.

Received 1st April 2021,
Accepted 4th June 2021

DOI: 10.1039/d1ma00296a

rsc.li/materials-advances

1. Introduction

Mechanochromic luminescence (MCL) materials with polychromatic switches can exhibit distinctly variational emission when subjected to external mechanical stimuli (e.g., smashing, grinding, stretching, or hydrostatic pressure).^{1–6} Such materials have been widely studied due to their potential applications in

optical data storage, pressure sensors, anti-counterfeiting inks, and optoelectronic devices.^{7–24} In general, MCL can be realized by chemical structure change (e.g., chemical bond destruction and recombination)^{25,26} or physical structure change (e.g., phase transition^{27–29} and conformational transition^{30–32}). The emission properties of MCL materials largely depend on molecular stacking modes, which are closely related to the molecular conformation and noncovalent interactions.^{33–35} External forces can change the molecular stacking mode, subsequently managing the emission colors and intensities.^{10–17,36,37}

Most MCL materials show reversible conversion luminescence under only one mechanical force.^{38–42} However, materials with distinct MCL responses towards different mechanical stimuli are very rare. For instance, Wang certificated that boron-diketonate crystals exhibited unique emissions under different mechanical stimuli, with a blue-shift after crushing and a red-shift under grinding and compressing.⁴³ Yamaguchi reported that a tetra-thiazolylthiophene fluorophore displayed distinctly emissive responses to mechanical grinding and hydrostatic pressures.⁴⁴

^a School of Materials Science and Engineering, Jiangsu Collaboration Innovation Center of Photovoltaic Science and Engineering, Jiangsu Engineering Laboratory of Light-Electricity-Heat Energy-Converting Materials and Applications, National Experimental Demonstration Center for Materials Science and Engineering, Changzhou University, Changzhou 213164, P. R. China.
E-mail: zhuwg18@126.com

^b State Key Laboratory of Superhard Materials, College of Physics, Jilin University, Changchun 130012, P. R. China

^c State Key Laboratory of Supramolecular Structure and Materials, College of Chemistry, Jilin University, Changchun 130012, P. R. China

† Electronic supplementary information (ESI) available. CCDC 2071819 and 2071820. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1ma00296a

(T_d , corresponding to 5% weight loss) of 418 °C and 428 °C, respectively (Fig. S1 in ESI[†]).

2.2. Crystal structures

Since molecular packing plays a key role in MCL, the crystal structures of **CzPL-PTZ** and **CzPL-tDPA** were deeply investigated, which might give important insights into the MCL mechanism. The yellow-green (533 nm) and blue-green (498 nm) photoluminescent (PL) peaks are observed for the **CzPL-PTZ** and **CzPL-tDPA** parent crystals made *via* vacuum sublimation (Fig. S2 in ESI[†]), respectively. Both parent crystals possess quantum yield (Φ_f) values of 39% and 66% correspond to fluorescence lifetimes ($\langle\tau\rangle$) of 12.07 ns and 16.56 ns for **CzPL-PTZ** and **CzPL-tDPA** (Fig. S3 and Table S1 in ESI[†]). Fig. 2 shows the crystal structures and intermolecular interactions of the **CzPL-PTZ** and **CzPL-tDPA** crystals measured by single crystal X-ray diffraction (XRD) experiments. Table S2 (ESI[†]) summarizes the detailed data of these crystal structures. The results indicate that **CzPL-PTZ** adopts a quasi-axial conformation and a regular head-to-tail arrangement throughout some C-H $\cdots\pi$, C-H \cdots N, C-H \cdots O, C-H \cdots S, and weak $\pi\cdots\pi$ interactions (Fig. 2a). In contrast, **CzPL-tDPA** features a head-to-tail arrangement but Z-shaped packing between adjacent molecules (Fig. 2b). These multiple intermolecular interactions can restrict the intramolecular motions and vibrations for both crystals, which is beneficial to the increase the Φ_f values. Moreover, the twisty molecular configurations with large dihedral angles between phenylene and phthalimide/carbazolyl (Fig. S4 in ESI[†]) and the $\pi\cdots\pi$ distance over 3.518 Å between anti-parallel molecules make both crystals present a weak $\pi\cdots\pi$ stacking interaction, in which the aggregation caused quenching (ACQ) can be efficiently suppressed. Their densities of 1.386 g cm⁻³ and 1.224 g cm⁻³ for **CzPL-PTZ** and **CzPL-tDPA** crystals indicate that the triclinic **CzPL-PTZ** crystal has much tighter stacking than the monoclinic **CzPL-tDPA** crystal. Interestingly, both crystals exhibit multiple intermolecular interactions observed from the *a*, *b*, *c* axes, and form a huge 3D short-range intermolecular interaction network (Fig. S5 in ESI[†]). Such short-range 3D networks with weak intermolecular interactions should be easy to be deformed and get distinct emissive responses under different mechanical forces (*e.g.*, crushing, grinding, or hydrostatic pressure).

2.1. Synthesis and characterization

Fig. 1 shows the chemical structures of **CzPL-PTZ** and **CzPL-tDPA**. Their synthetic routes are shown in Scheme S1 ESI[†]. They were synthesized by the Buchwald-Hartwig C–N cross-coupling reaction between **CzPL-Br** and PTZ or tDPA in moderate yields. Subsequently, they were purified *via* vacuum sublimation. Their molecular structures were fully characterized by ¹H, ¹³C NMR spectroscopy and TOF-MS (see ESI[†]). Thermogravimetric analysis (TGA) measurements indicate that both **CzPL-PTZ** and **CzPL-tDPA** have good thermal stability with high decomposition temperatures

2.3. Photophysical properties

The UV-Visible and PL spectra of **CzPL-PTZ** and **CzPL-tDPA** were obtained in their solutions with different solvents and neat films. Two typical absorption bands were observed in Fig. S6 (ESI[†]), which contain a high-lying band of absorption in the range of 300–350 nm and a low-lying band of absorption in the range of 350–450 nm. The low-lying bands of absorption are ascribed to the intramolecular charge transfer (ICT) absorption.^{49–51} Fig. S6 (ESI[†]) also shows the PL spectra of **CzPL-PTZ** and **CzPL-tDPA** in different solvents (1.0×10^{-5} M). Dual emissions were observed for **CzPL-PTZ** in toluene (Tol), chloroform (CF), and tetrahydrofuran (THF), which were assigned to the dual conformers of PTZ (Fig. S6a in ESI[†]).⁵² The excitation spectra of **CzPL-PTZ** at 480 nm and 560 nm in the CF solvent (1.0×10^{-5} M) with different spectra indicate that the two emission bands at

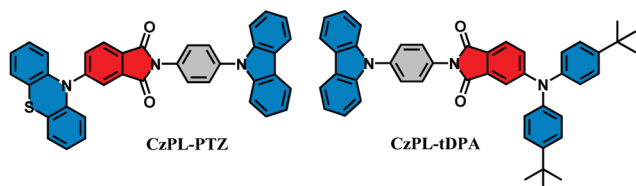


Fig. 1 Chemical structures of **CzPL-PTZ** and **CzPL-tDPA**.

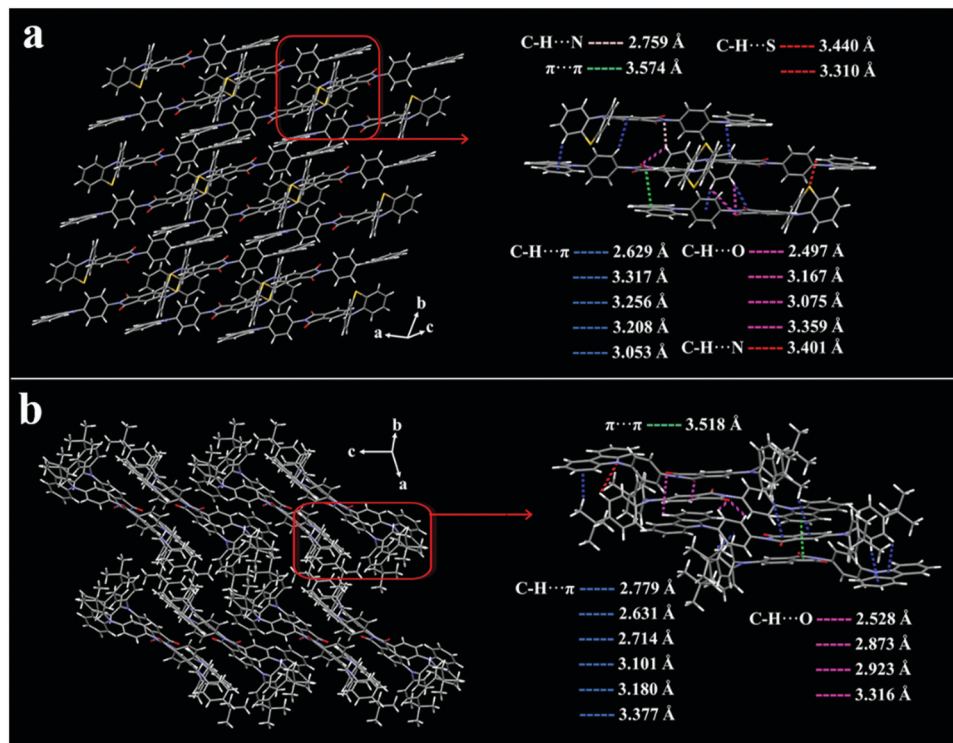


Fig. 2 Crystal structures and intermolecular interactions of the (a) **CzPL-PTZ** and (b) **CzPL-tDPA** crystals.

480 nm and 560 nm come from different excited states, *i.e.* locally excited (LE) and CT states (Fig. S7 in ESI[†]).^{52–58} In contrast, there is only single emission peak for **CzPL-tDPA** in different solutions (Fig. S6b in ESI[†]). Both molecules show obvious solvent dependence in different polar solvents owing to their ICT effects. In addition, different PL spectra are observed for both molecules under two solid states. Due to the special quasi-axial conformation of the PTZ unit (bending to one side, small steric hindrance), the linear **CzPL-PTZ** molecules are easy to pile up in the long-range order and exhibit relatively strong intermolecular interactions. In contrast, **CzPL-tDPA** can easily form a large twisty type between **tDPA** and **CzPL**, which results in a relatively weak intermolecular interaction owing to the large steric hindrance of *tert*-butyl. Therefore, **CzPL-PTZ** displayed more red-shifted luminescence than **CzPL-tDPA** in crystal and film states (Fig. S2 and S8 in ESI[†]).⁵⁶

2.4. Theoretical calculations

Density functional theory (DFT) discloses that the asymmetric D–A–D' strategy has an impact on the lowest-lying electronic transition. The electronic structures of **CzPL-PTZ** and **CzPL-tDPA** are optimized at the ground state (S_0) in the gas state using Gaussian 09W program at the B3LYP/6-31G (d)/LanL2DZ level.^{59,60} As shown in Fig. S9 (ESI[†]), the lowest unoccupied molecular orbitals (LUMOs) of **CzPL-PTZ** and **CzPL-tDPA** are mainly located on electron deficient phthalimide moieties, and the highest occupied molecular orbital (HOMO) of **CzPL-PTZ** is dominantly distributed over the electron donor phenothiazine moieties. Since carbazole has stronger electron donating ability than bis (4-*tert*-butyl) phenyl) amine, the HOMO of **CzPL-tDPA** is mainly distributed in the

carbazole unit.⁶¹ Clearly, electron-donating D' units with distinguishing ability led to distinction in the molecular level and hence influence the MCL properties in the aggregation state. In addition, the calculated HOMO and LUMO energy levels are $-5.28/-2.63$ eV and $-5.18/-2.08$ eV for **CzPL-PTZ** and **CzPL-tDPA**, respectively. The more effective spatial separation of HOMO and LUMO in the **CzPL-PTZ** compound compared with **CzPL-tDPA** should demonstrate stronger ICT nature.⁶²

2.5. Electrochemical characterization

Electrochemical properties of **CzPL-PTZ** and **CzPL-tDPA** were investigated by cyclic voltammetry (CV) adopting ferrocene as a reference standard in anhydrous CH_3CN solutions. The recorded CV curves are shown in Fig. S10 (ESI[†]) and their electrochemical data are listed in Table S4 (see ESI[†]); **CzPL-PTZ** and **CzPL-tDPA** present reversible oxidation process in CV curves. According to the onset voltages of the oxidation curves, their HOMO levels are determined to be -5.16 and -5.41 eV for **CzPL-PTZ** and **CzPL-tDPA**, respectively. The lowest unoccupied molecular orbital (LUMO) energy level of **CzPL-PTZ** and **CzPL-tDPA** can be calculated using E_{HOMO} and optical band gap (E_g), which are -2.04 and -2.48 eV, respectively.^{63,64} In addition, the calculated HOMO and LUMO energy levels for **CzPL-PTZ** and **CzPL-tDPA** are $-5.28/-2.63$ eV and $-5.18/-1.18$ eV, respectively, which are reasonable deviations from the experimental data.


2.6. Mechanochromic luminescence properties

The MCL properties of the **CzPL-PTZ** and **CzPL-tDPA** crystals were studied under different forces, such as tensile force,



When the crushed crystals are further ground by a mortar, the resulting ground sample of **CzPL-tDPA** shows bathochromic-shift emission like most of the reported MCL materials.^{13,14,27–31} However, the ground sample of **CzPL-PTZ** shows a rare hypochromic-shift emission.^{21,23,24,66} A broad emission band peak at 501 nm is observed in the **CzPL-PTZ** ground sample, which is blue-shifted by 18 nm in comparison with that of the **CzPL-PTZ** crushed crystal (519 nm). Under further fuming the ground samples with the polar solvent vapor of DCM for 10 min, the resulting **CzPL-PTZ** fumed

The powder X-ray diffraction (PXRD) diagrams of **CzPL-PTZ** and **CzPL-tDPA** in different states indicate that these various MCL responses are related to the change in the molecular packing structure, which are recorded in Figs S14a and b (ESI[†]), respectively. The results show that **CzPL-PTZ** and **CzPL-tDPA** form different molecular stacking architectures over the crushing-grinding-fuming treatment. These observations indicate that the strong and few diffraction peaks of **CzPL-PTZ** and **CzPL-tDPA** in the parent crystal state indicate that their crystals are polycrystalline. After crushing, the stacked polycrystals are split, the crystal size becomes smaller and the diffraction peaks increase. With further grinding, the PXRD pattern of the ground sample of **CzPL-PTZ** and **CzPL-tDPA** are composed of several blunt “peaks”, indicating that they are mainly amorphous in the ground state or their crystallites are extremely small in size.

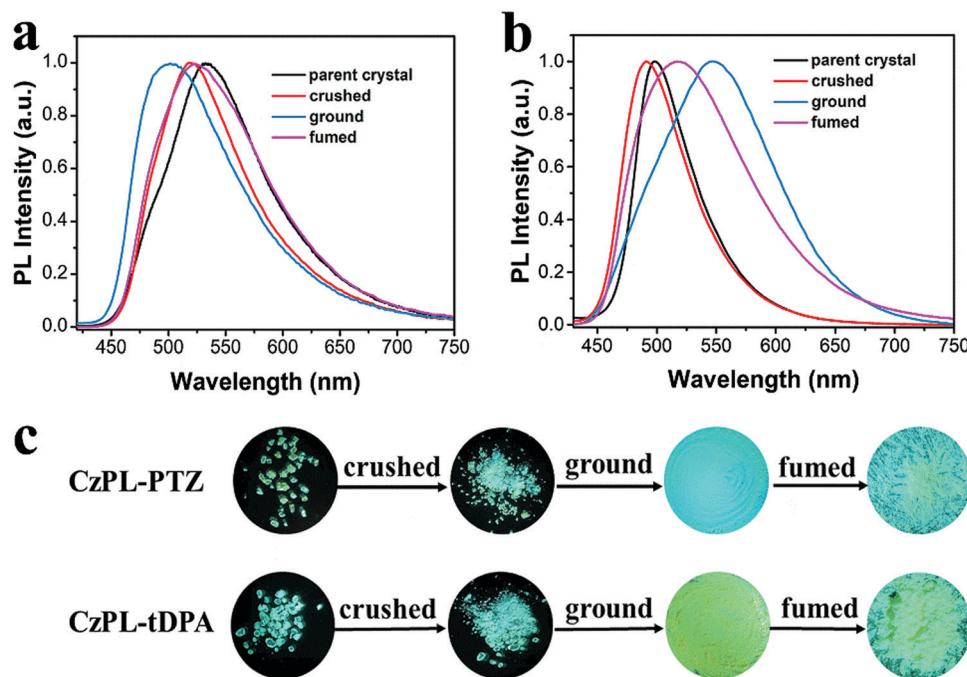

© 2021 The Author(s). Published by the Royal Society of Chemistry

Similarly, the ground samples of **CzPL-PTZ** and **CzPL-tDPA** after fumigation in dichloromethane (DCM) vapor for 10 min exhibit almost same PXRD patterns as those of single crystal simulation, indicating that the molecular arrangement in fumigated samples return to the crystalline state. There is no doubt that the molecular arrangement of **CzPL-PTZ** and **CzPL-tDPA** changed during mechanical grinding. For the crystal **CzPL-PTZ**, grinding may cause the aggregated molecules to slip, disrupt the 3D short range intermolecular interaction network to ongoing single molecules, which will lead to the blue-shift emission.⁴⁴ The red-shift luminescence of **CzPL-tDPA** may be due to the different molecular arrangements such as π -stacked dimers have been formed after grinding.^{13,14,43}

As mentioned above, the anisotropic pressure causes the **CzPL-PTZ** and **CzPL-tDPA** crystals to exhibit distinct MCL. To reveal the effects of isotropic pressure on emission, the PL spectra of both parent crystals under different hydrostatic pressures were further studied. As shown in Fig. 4, the **CzPL-PTZ** crystal exhibits a gradually red-shifted and weakened emission from 480 to 600 nm, with the hydrostatic pressure increasing from ambient pressure to 10.31 GPa. Furthermore, its absorption is also observed to maintain a red-shifted trend (Fig. S15 in ESI[†]). In contrast, when the hydrostatic pressure is returned to ambient pressure, its PL

spectrum turns back to the original PL profile (Fig. 4b). Identically, **CzPL-tDPA** shows similarly red-shifted emission and absorption with the increase in the hydrostatic pressure (Fig. 5 and Fig. S16 in ESI[†]). However, the PL spectrum of **CzPL-tDPA** just partly returns to the initial PL profile after the hydrostatic pressure is released to ambient pressure. More interestingly, whether it pressuring or decompressing the crystal, the emissive wavelength and energy have a direct good linear relationship to the hydrostatic pressure for both crystals (Fig. S17 and S18 in ESI[†]). This emissive uniqueness endows this type of MCL materials with potential application in pressure sensors.⁵ Better emissive restorability of both crystals indicates that the molecular packing mode should not change substantially during a high-pressure process. Considering this point, the intense red-shift and weakened PL of both crystals may be attributed to the pressure-induced conformational planarization with increasing pressure, which leads to severe π - π intermolecular interactions.^{67,68}

According to the crystal structure analysis, there are weak π - π interactions in both crystals. The π - π distances of **CzPL-PTZ** and **CzPL-tDPA** are 3.574 Å and 3.518 Å, respectively, which are beyond the range of van der Waals interaction (Fig. 2b–d). The molecular distance between adjacent molecules should be shortened and π - π interaction should be enhanced with increasing pressure.

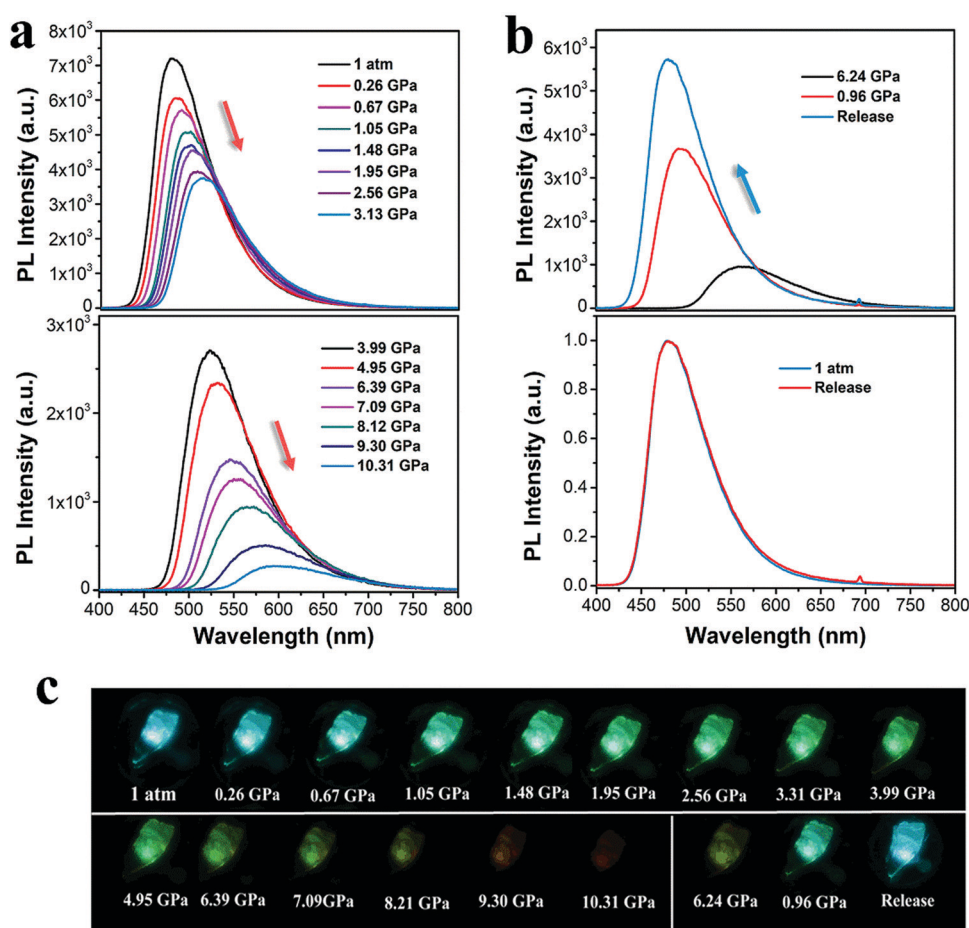


Fig. 4 (a) PL spectra of crystal **CzPL-PTZ** under the pressures from 1 atm to 10.31 GPa, (b) PL spectra of crystal **CzPL-PTZ** during the decompression processes, (c) the fluorescence images of the **CzPL-PTZ** crystal under photo excitation at 350 nm and different pressures.



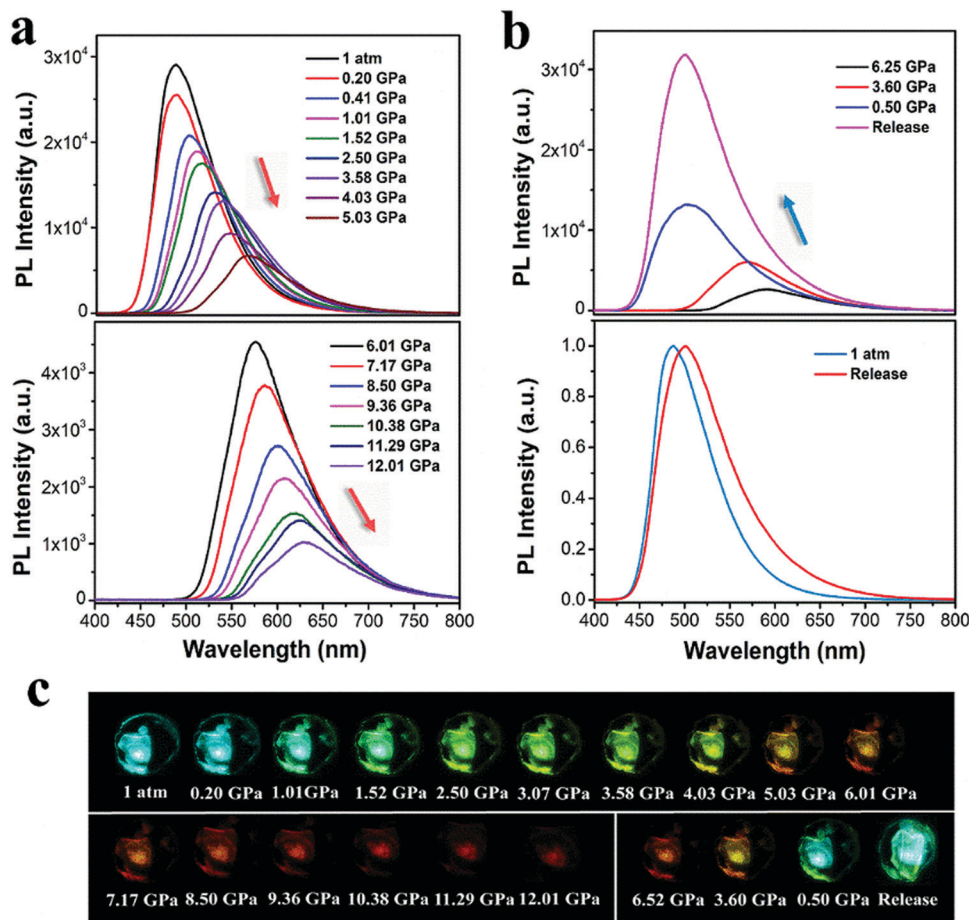


Fig. 5 (a) PL spectra of crystal **CzPL-tDPA** under the pressures from 1 atm to 12.01 GPa, (b) PL spectra of crystal **CzPL-tDPA** during the decompression processes, (c) the fluorescence images of the crystal **CzPL-tDPA** under photo excitation at 350 nm and different pressures.

As a result, red-shifted and weakened emissions are observed. The squashed **CzPL-PTZ** crystal can rebound to its original shape after decompressing. That is, its 3D intermolecular short-range interaction network undergoes a simple harmonic vibration within a certain pressure range during the compression-decompression process. Alternatively, the deformation of a 3D intermolecular short-range interaction network is reversible in this condition. Regarding the behavior of the **CzPL-tDPA** crystal under decompression, it might have to overcome some potential barrier to recover the 3D intermolecular short-range interaction network. Such an incomplete recovery is partially caused by the lattice vibration under high pressure.⁶⁹

3. Conclusion

In summary, we have demonstrated a simple and effective molecular design strategy by integrating the distinguishing ability of electron-donating units (D') on the **CzPL** scaffold to obtain two novel MCL materials of **CzPL-PTZ** and **CzPL-tDPA**. The D' units of pseudo-planar PTZ and propeller-like tDPA play an important role in the MCL properties of **CzPL-PTZ** and **CzPL-tDPA** parent crystals. As a result, both crushed crystals show an abnormal blue-shifted emission under tensile force in comparison with

corresponding parent crystals; **CzPL-PTZ** crystals exhibit hypochromatic-shift, while **CzPL-tDPA** exhibit bathochromic shift when under anisotropic pressure. In contrast, both crystals show a red-shifted emission under increasing isotropic pressures. Significantly distinct MCL for both parent crystals under tensile force, anisotropic and isotropic pressures certify the effectiveness of the strategy D-A-D' scaffold. Interestingly, crystal **CzPL-PTZ** can completely return to the initial state after decompression, while crystal **CzPL-tDPA** cannot fully recover to its original state after removing pressure. More importantly, there is a linear relationship between emissive wavelength and pressure. The distinct and interesting MCL phenomena may have a potential application in pressure sensors and data storage.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (52073035, U1663229, and 21725304), the Top-notch Academic Programs Project (TAPP) for Polymeric



Materials Science and Technology and the Priority Academic Program Development (PAPD) of Jiangsu Higher Education Institutions, the Jiangsu Provincial Talents Project of High-Level Innovation and Entrepreneurship, the Research Innovation Program for Postgraduate of Jiangsu Province (SJCX20_0973).

References

- 1 T. Seki, Y. Takamatsu and H. Ito, *J. Am. Chem. Soc.*, 2016, **138**, 6252–6260.
- 2 Y. J. Dong, B. Xu, J. B. Zhang, X. Tan, L. J. Wang, J. L. Chen, H. G. Lv, S. P. Wen, B. Li, L. Ye, B. Zou and W. J. Tian, *Angew. Chem., Int. Ed.*, 2012, **51**, 10782–10785.
- 3 L. Y. Bai, P. Bose, Q. Gao, Y. X. Li, R. Ganguly and Y. L. Zhao, *J. Am. Chem. Soc.*, 2017, **139**, 436–441.
- 4 B. J. Xu, Y. X. Mu, Z. Mao, Z. L. Xie, H. Z. Wu, Y. Zhang, C. J. Jin, Z. G. Chi, S. W. Liu, J. R. Xu, Y.-C. Wu, P.-Y. Lu, A. Lien and M. R. Bryce, *Chem. Sci.*, 2016, **7**, 2201–2206.
- 5 T. Ono, Y. Tsukiyama, A. Taema, H. Sato, H. Kiyooka, Y. Yamaguchi, A. Nagahashi, M. Nishiyama, Y. Akahama, Y. Ozawa, M. Abe and Y. Hisaeda, *ChemPhotoChem*, 2018, **2**, 416–420.
- 6 Y. Sagara, T. Mutai, I. Yoshikawa and K. Araki, *J. Am. Chem. Soc.*, 2007, **129**, 1520–1521.
- 7 Z. G. Chi, X. Q. Zhang, B. J. Xu, X. Zhou, C. P. Ma, Y. Zhang, S. W. Liu and J. R. Xu, *Chem. Soc. Rev.*, 2012, **41**, 3878–3896.
- 8 P. Theato, B. S. Sumerlin, R. K. O'Reilly and T. H. Epps III, Stimuli responsive materials, *Chem. Soc. Rev.*, 2013, **42**, 7055–7056.
- 9 Y. Sagara, S. Yaman, M. Mitani, C. Weder and T. Kato, *Adv. Mater.*, 2016, **28**, 1073–1095.
- 10 C. Wang and Z. Li, *Mater. Chem. Front.*, 2017, **1**, 2174–2194.
- 11 S.-J. Yoon, J. W. Chung, J. Gierschner, K. S. Kim, M.-G. Choi, D. Kim and S.-Y. Park, *J. Am. Chem. Soc.*, 2010, **132**, 13675–13683.
- 12 Y.-B. Gong, P. Zhang, Y.-R. Gu, J.-Q. Wang, M.-M. Han, C. Chen, X.-J. Zhan, Z.-L. Xie, B. Zou, Q. Peng, Z.-G. Chi and Z. Li, *Adv. Opt. Mater.*, 2018, **6**, 1800198.
- 13 T. Ito, T. Saito, N. Oshima, N. Kitamura, S. Ishizaka, Y. Hinatsu, M. Wakeshima, H. Yukio, M. Kato, K. Tsuge and M. Sawamura, *J. Am. Chem. Soc.*, 2008, **130**, 10044–10045.
- 14 Q. K. Qi, J. Y. Qian, X. Tan, J. B. Zhang, L. J. Wang, B. Xu, B. Zou and W. J. Tian, *Adv. Funct. Mater.*, 2015, **25**, 4005–4010.
- 15 Y. Sagara and T. Kato, *Angew. Chem., Int. Ed.*, 2008, **120**, 5253–5256.
- 16 Y. Sagara, S. Yamane, T. Mutai, K. Araki and T. Kato, *Adv. Funct. Mater.*, 2009, **19**, 1869–1875.
- 17 Y. Sagara and T. Kato, *Angew. Chem., Int. Ed.*, 2011, **50**, 9128–9132.
- 18 F. Ciardelli, G. Ruggeri and A. Pucci, *Chem. Soc. Rev.*, 2013, **42**, 857–870.
- 19 K. M. Wiggins, J. N. Brantley and C. W. Bielawski, *Chem. Soc. Rev.*, 2013, **42**, 7130–7147.
- 20 A. Lavrenova, D.-W. Balkenende, Y. Sagara, S. Schrettl, Y. C. Simon and C. Weder, *J. Am. Chem. Soc.*, 2017, **139**, 4302–4305.
- 21 D. P. Yan, H. J. Yang, Q. Y. Meng, H. Y. Lin and M. Wei, *Adv. Funct. Mater.*, 2014, **24**, 587–594.
- 22 Y. Matsunaga and J.-S. Yang, *Angew. Chem., Int. Ed.*, 2015, **54**, 7985–7989.
- 23 Y. J. Liu, Q. X. Zeng, B. Zou, Y. Liu, B. Xu and W. J. Tian, *Angew. Chem., Int. Ed.*, 2018, **57**, 15670–15674.
- 24 H. C. Liu, Y. R. Gu, Y. X. Dai, K. Wang, S. T. Zhang, G. Chen, B. Zou and B. Yang, *J. Am. Chem. Soc.*, 2020, **142**, 1153–1158.
- 25 J. W. Chung, Y. You, H. S. Huh, B. K. An, S.-J. Yoon, S. Kim, H. Kim, S. W. Lee and S. Y. Park, *J. Am. Chem. Soc.*, 2009, **131**, 8163–8172.
- 26 Y. Wang, X. Tan, Y. M. Zhang, S. Zhu, I. Zhang, B. Yu, K. Wang, B. Yang, M. Li, B. Zou and S. X. Zhang, *J. Am. Chem. Soc.*, 2015, **137**, 931–939.
- 27 H. Ito, M. Muromoto, S. Kurenuma, S. Ishizaka, N. Kitamura, H. Sato and T. Seki, *Nat. Commun.*, 2013, **4**, 2009.
- 28 G. Q. Zhang, J. W. Lu, M. Sabat and C. Fraser, *J. Am. Chem. Soc.*, 2010, **132**, 2160–2162.
- 29 M. Tanioka, S. Kamino, A. Muranaka, Y. Ooyama, H. Ota, Y. Shirasaki, J. Horigome, M. Ueda, M. Uchiyama, D. Sawada and S. Enomoto, *J. Am. Chem. Soc.*, 2015, **137**, 6436–6439.
- 30 J. Wang, J. Mei, R. Hu, J. Z. Sun, A. Qin and B. Z. Tang, *J. Am. Chem. Soc.*, 2012, **134**, 9956–9966.
- 31 W. Z. Yuan, Y. Tan, Y. Gong, P. Lu, J. W. Lam, X. Y. Shen, C. Feng, H. H. Sung, Y. Lu, I. D. Williams, J. Z. Sun, Y. Zhang and B. Z. Tang, *Adv. Mater.*, 2013, **25**, 2837–2843.
- 32 Y. J. Zhang, Q. B. Song, K. Wang, W. G. Mao, F. Cao, J. W. Sun, L. L. Zhan, Y. K. Lv, Y. G. Ma, B. Zou and C. Zhang, *J. Mater. Chem. C*, 2015, **3**, 3049–3054.
- 33 D. P. Yan and D. G. Evans, *Mater. Horiz.*, 2014, **1**, 46–57.
- 34 Z. Y. Ma, M. J. Teng, Z. J. Wang, S. Yang and X. R. Jia, *Angew. Chem., Int. Ed.*, 2013, **52**, 12268–12272.
- 35 S. K. Park, J. H. Kim, T. Ohto, R. Yamada, A. O. F. Jones, D. R. Whang, I. Cho, S. Oh, S. H. Hong, J. E. Kwon, J. H. Kim, Y. Olivier, R. Fischer, R. Resel, J. Gierschner, H. Tada and S. Y. Park, *Adv. Mater.*, 2017, **29**, 1701346.
- 36 P.-Z. Chen, J.-X. Wang, L.-Y. Niu, Y.-Z. Chen and Q.-Z. Yang, *J. Mater. Chem. C*, 2017, **5**, 12538–12546.
- 37 S. Xu, T. Liu, Y. Mu, Y.-F. Wang, Z. Chi, C.-C. Lo, S. Liu, Y. Zhang, A. Lien and J. Xu, *Angew. Chem., Int. Ed.*, 2015, **54**, 874–878.
- 38 C. D. Dou, L. Han, S. S. Zhao, H. Y. Zhang and Y. Wang, *J. Phys. Chem. Lett.*, 2011, **2**, 666–670.
- 39 Z. L. Zhang, D. D. Yao, T. L. Zhou, H. Y. Zhang and Y. Wang, *Chem. Commun.*, 2011, **47**, 7782–7784.
- 40 Q. Benito, X. F. Le Goff, S. Maron, A. Fargues, A. Garcia, C. Martineau, F. Kahlal, S. Taulelle, T. Gacoin, J.-P. Boilot and S. Perruchas, *J. Am. Chem. Soc.*, 2014, **136**, 11311–11320.
- 41 X. Luo, J. N. Li, C. H. Li, L. P. Heng, Y. Q. Dong, Z. P. Liu, Z. Bo and B. Z. Tang, *Adv. Mater.*, 2011, **23**, 3261–3265.
- 42 J. Luo, L.-Y. Li, Y. L. Song and J. Pei, *Chem. – Eur. J.*, 2011, **17**, 10515–10519.
- 43 L. Wang, K. Wang, B. Zou, K. Q. Ye, H. Y. Zhang and Y. Wang, *Adv. Mater.*, 2015, **27**, 2918–2922.
- 44 K. Nagura, S. Saito, H. Yusa, H. Yamawaki, H. Fujihisa, H. Sato, Y. Shimoikeda and S. Yamaguchi, *J. Am. Chem. Soc.*, 2013, **135**, 10322–10325.
- 45 Y. Y. Qin, G. P. Li, T. Qi and H. Huang, *Mater. Chem. Front.*, 2020, **4**, 1554–1568.



- 46 H. Nakayama, J.-i. Nishida, N. Takada, H. Sato and Y. Yamashita, *Chem. Mater.*, 2012, **24**, 671–676.
- 47 J. Nishida, H. Ohura, Y. Kita, H. Hasegawa, T. Kawase, N. Takada, H. Sato, Y. Sei and Y. Yamashita, *J. Org. Chem.*, 2016, **81**, 433–441.
- 48 J. A. Li, J. H. Zhou, Z. Mao, Z. L. Xie, Z. Yang, B. J. Xu, C. Liu, X. Chen, D. Y. Ren, H. Pan, G. Shi, Y. Zhang and Z. G. Chi, *Angew. Chem., Int. Ed.*, 2018, **57**, 6449–6453.
- 49 Z. Mao, Z. Yang, C. Xu, Z. Xie, L. Jiang, F. L. Gu, J. Zhao, Y. Zhang, M. P. Aldred and Z. G. Chi, *Chem. Sci.*, 2019, **10**, 7352–7357.
- 50 S. Y. Lee, T. Yasuda, Y. S. Yang, Q. Zhang and C. Adachi, *Angew. Chem., Int. Ed.*, 2014, **53**, 6402–6406.
- 51 P. Rajamalli, N. Senthilkumar, P. Gandeepan, P. Y. Gandeepan, P.-Y. Huang, M.-J. Huang, C.-Z. Ren-Wu, C.-Y. Yang, M.-J. Chiu, L.-K. Chu, H.-W. Lin and C.-H. Cheng, *J. Am. Chem. Soc.*, 2016, **138**, 628–634.
- 52 H. Tanaka, K. Shizu, H. Nakanotani and C. Adachi, *J. Phys. Chem. C*, 2014, **118**, 15985–15994.
- 53 D.-G. Chen, T.-C. Lin, Y.-A. Chen, T.-C. Lin, Y.-T. Chen and P.-T. Chou, *J. Phys. Chem. C*, 2018, **122**, 12215–12221.
- 54 K. Wang, Y.-Z. Shi, C.-J. Zheng, W. Liu, K. Liang, M. Zhang, H. Lin, S.-L. Tao, C.-S. Lee, X.-M. Ou and X.-H. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 31515–31525.
- 55 B. Li, Z. Li, F. Gou, J. Song, X. Jiang, Y. Wang, S. Gao, J. Wang, X. Pang, L. Zhao and Y. Zhang, *ACS Appl. Mater. Interfaces*, 2020, **12**, 14233–14243.
- 56 J. F. Li, C. X. Hou, C. Huang, S. Q. Xu, X. L. Peng, Q. Qi, W.-Y. Lai and W. Huang, *Research*, 2020, 3839160.
- 57 J. F. Li, C. L. Yang, X. L. Peng, Y. Chen, Q. Qi, X. Y. Luo, W.-Y. Lai and W. Huang, *J. Mater. Chem. C*, 2018, **6**, 19–28.
- 58 Y. Wan, J. F. Li, X. L. Peng, C. Huang, Q. Qi, W.-Y. Lai and W. Huang, *RSC Adv.*, 2017, **7**, 35543–35548.
- 59 Z. Yang, Y. Zhang, Z. Qiu, J. Zeng, J. Guo, S. Hu, Z. Zhao, X. Li, S. Ji, Y. Huo and S.-J. Su, *ACS Appl. Mater. Interfaces*, 2020, **12**, 29528–29539.
- 60 J.-H. Tan, W.-C. Chen, S.-F. Ni, Z. Qiu, Y. Zhang, Z. Yang, C. Cao, Y. Huo and C.-S. Lee, *J. Mater. Chem. C*, 2020, **8**, 8061–8068.
- 61 Y. Im, M. Kim, Y. J. Cho, J.-A. Seo, K. S. Yook and J. Y. Lee, *Chem. Mater.*, 2017, **29**, 1946–1963.
- 62 R. S. Nobuyasu, J. S. Ward, J. Gibson, B. A. Laidlaw, Z. J. Ren, P. Data, A. S. Batsanov, T. J. Penfold, M. R. Bryce and F. B. Dias, *J. Mater. Chem. C*, 2019, **7**, 6672–6684.
- 63 C. Y. Wang, J. Zhang, G. K. Long, N. Aratani, H. Yamada, Y. Zhao and Q. C. Zhang, *Angew. Chem., Int. Ed.*, 2015, **54**, 6292–6296.
- 64 K. L. Wu, T. Zhang, L. Zhan, C. Zhong, S. L. Gong, Z. H. Lu and C. L. Yang, *Adv. Opt. Mater.*, 2016, **4**, 1558–1566.
- 65 R. Katoh, K. Suzuki, A. Furube, M. Kotani and K. Tokumaru, *J. Phys. Chem. C*, 2009, **113**, 2961–2965.
- 66 G. He, L. L. Du, Y. Y. Gong, Y. L. Liu, C. B. Yu, C. Wei and W. Z. Yuan, *ACS Omega*, 2019, **4**, 344–351.
- 67 H. S. Yuan, K. Wang, K. Yang, B. B. Liu and B. Zou, *J. Phys. Chem. Lett.*, 2014, **5**, 2968–2973.
- 68 J. P. Schmidtke, J. S. Kim, J. Gierschner, C. Silva and R. H. Friend, *Phys. Rev. Lett.*, 2007, **99**, 167401.
- 69 Y. Li, Z. Y. Ma, A. Li, W. Q. Xu, Y. C. Wang, H. Jiang, K. Wang, Y. S. Zhao and X. R. Jia, *ACS Appl. Mater. Interfaces*, 2017, **9**, 8910–8918.

