

COMMUNICATION

[View Article Online](#)
[View Journal](#) | [View Issue](#)

Cite this: *Dalton Trans.*, 2022, **51**, 8583

Received 28th April 2022,

Accepted 18th May 2022

DOI: 10.1039/d2dt01337a

rsc.li/dalton

Strong magnetic exchange coupling in a radical-bridged trinuclear nickel complex†

Luming Yang, Julius J. Oppenheim  and Mircea Dincă *

Reaction of 2,3,6,7,10,11-hexaaminotriphenylene hexahydrochloride (HATP·6HCl) and (Tp^{Ph}Ni)Cl (Tp^{Ph} = tris(3,5-diphenyl-1-pyrazolyl)borate) produces the radical-bridged trinuclear complex [(Tp^{Ph}Ni)₃(HITP)] (HITP^{3-·} = 2,3,6,7,10,11-hexaiminotriphenylene). Magnetic measurements and broken-symmetry density functional theory calculations reveal strong exchange coupling persisting at room temperature between HITP^{3-·} and two of the three Ni²⁺ centers, a rare example of strong radical-mediated magnetic coupling in multimetallic complexes. These results demonstrate the potential of radical-bearing tritopic HITP ligands as building blocks for extended molecule-based magnetic materials.

Introduction

Radical-mediated coupling of paramagnetic spin centers is an effective strategy for developing molecule-based magnetic materials, including high-temperature multifunctional magnets,^{1–3} switchable porous magnetic sensors,^{4,5} and low-dimensional compounds with slow relaxation dynamics,^{6,7} because coupling in such compounds can give rise to strong and long-range magnetic interactions through the direct exchange mechanisms.^{3,8} To date, many ditopic radical-containing ligand bridges have been reported to mediate strong coupling persistent at room-temperature in transition-metal complexes.^{9–13} In comparison, trimetallic complexes with tritopic radical bridges, a common topological component for solid-state magnets as well as high-spin-state molecular magnets, are rare and often experience weaker coupling.^{3,6,14–16} One promising candidate for a tritopic radical bridge that could mediate strong coupling through π -type delocalized radicals is the trianionic 2,3,6,7,10,11-hexaiminotriphenylene (HITP^{3-·}),¹⁷ a tritopic congener of the

radical anion *o*-benzosemiquinone diimine (BQDI) that is known for strong magnetic exchange coupling with transition metal centers.⁶

Here, we report the synthesis of [(Tp^{Ph}Ni)₃(HITP^{3-·})], **1** (Tp^{Ph} = tris(3,5-diphenyl-1-pyrazolyl)borate), a trimetallic cluster containing Ni²⁺ centers and an HITP-centered radical. Notably, magnetic measurements reveal strong Ni–HITP coupling between HITP^{3-·} and two Ni²⁺ spins that persists at room temperature. This interaction is much stronger than the previously reported metal–ligand spin coupling in the oxygen analogs, [(Tp^{Ph}Ni)₃(HOTP^{3-·})] (**2**)¹⁸ and [(Me₃TPANi)₃(HOTP^{3-·})] (**3**)¹⁹ (Me₃TPA = *N,N,N*-tris[(6-methyl-2-pyridyl)methyl]amine), and is attributed to strong orbital delocalization between Ni²⁺ and the nitrogen atoms on HITP. These results provide inspiration for the rational design of new room-temperature magnetic materials.

Results and discussion

Complex **1** was synthesized by deprotonation of 2,3,6,7,10,11-hexaaminotriphenylene hexahydrochloride with tetrabutylammonium hydroxide under an atmosphere of N₂, followed by reaction with (Tp^{Ph}Ni)Cl in air in a dichloromethane–methanol mixture. Dark purple crystals were obtained in 45% yield by layering *n*-hexane onto a solution of **1** in dichloromethane (Scheme S1†). High resolution electrospray ionization/mass spectrometry (ESI/MS) revealed an M⁺ peak at *m/z* = 2496.8, which together with microelemental analysis confirmed the identity and purity of **1** (Fig. S1†).

Compound **1** crystallizes in the *P* $\bar{1}$ space group, and displays three crystallographically independent Ni atoms. Two of the Ni ions exhibit square pyramidal (SP) geometry, and the third one has trigonal bipyramidal geometry (TBP) (Fig. 1). All Ni centers experience slight distortion from the respective ideal geometries, reflected by the non-zero continuous-shape measurement parameters (Tables S5–S7† and related discussion).²⁰ The bulky κ^3 -chelating Tp^{Ph} capping ligands magneti-

Department of Chemistry, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, MA 02139, USA. E-mail: Mdinc@mit.edu

† Electronic supplementary information (ESI) available. CCDC 2109142. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2dt01337a>

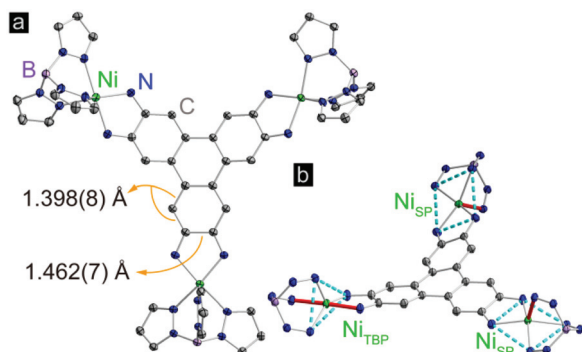


Fig. 1 (a) X-ray crystal structure of $[(\text{Tp}^{\text{Ph}}\text{Ni})_3(\text{HITP})]$. (b) Highlight of the coordination environments of the Ni centers. Turquoise dashed lines mark the trigonal and tetragonal planes for Ni_{TBP} and Ni_{SP} . Ni–N bonds along the high-symmetry axes are colored pink. Thermal ellipsoids are plotted at 50% probability. Hydrogen atoms, phenyl groups, and solvent molecules are omitted for clarity.

cally isolate individual Ni_3HITP units from neighboring molecules. The average Ni– N_{TP} bond length, 2.063(6) Å, is in line with the values reported for high-spin Ni^{2+} complexes capped by Tp derivatives.²¹ The average length of the C–C bonds forming Ni–N–C–C–N metallocycles with each phenylenediamine arm within HITP is 1.462(7) Å, much longer than the adjacent C–C bond within the same aromatic ring, 1.398(8) Å (Fig. 1). This reflects a significant distortion of each phenylenediamine ring and evidences the “bisallyl”-type configuration resulting from the oxidation of a fully deprotonated HITP^{6-} moiety to HITP^{3-} (Scheme S2†).²² For metal–diamine complexes, the degree of oxidation on the diamine fragment is also reflected in the C–N bond lengths.²² In **1**, the average C– N_{HITP} bond length, 1.322(6) Å, lies between that of trimetallic complexes with the fully-reduced HITP^{6-} (1.39–1.40 Å) and the more oxidized HITP^{2-} (1.305(6) Å), as may be expected for an intermediate oxidation in HITP^{3-} .^{23,24} Finally, although the Ni–N–C–C–N metallocycles are nearly planar, the triphenylene core of HITP^{3-} experiences significant distortion from planarity, with dihedral angles of 20.9°, 26.7°, and 40.1° between pairs of planes defined by the three Ni–N–C–C–N metallocycles (Fig. S2†). Such distortions are not uncommon in large aromatic systems and have been assigned to Jahn–Teller and crystal packing effects.²⁵

Cyclic voltammetry (CV) provided further evidence in assigning the formal oxidation state of HITP and offered clues on the electronic delocalization in **1**. CV measurements in 0.15 M solution of tetrabutylammonium hexafluorophosphate (TBAPF_6) in tetrahydrofuran (THF) under a N_2 atmosphere reveal quasi-reversible electron transfer events centered at –1.41, –0.69, –0.10, and 0.10 V with respect to the ferrocene/ferrocene couple (Fc^+/Fc , Fig. 2 and Table S1†). These values are comparable to ligand-centered redox events for other trimetallic HXTP compounds ($\text{X} = \text{I}, \text{O}$), and are therefore assigned to the $\text{HITP}^{4-/-5-}$, $\text{HITP}^{3-/-4-}$, $\text{HITP}^{2-/-3-}$, and $\text{HITP}^{-/2-}$ redox couples.^{18,24,26} In the context of classical mixed-valence theory, which relates electrochemical redox potentials to the degree of electronic delocalization, the potential difference

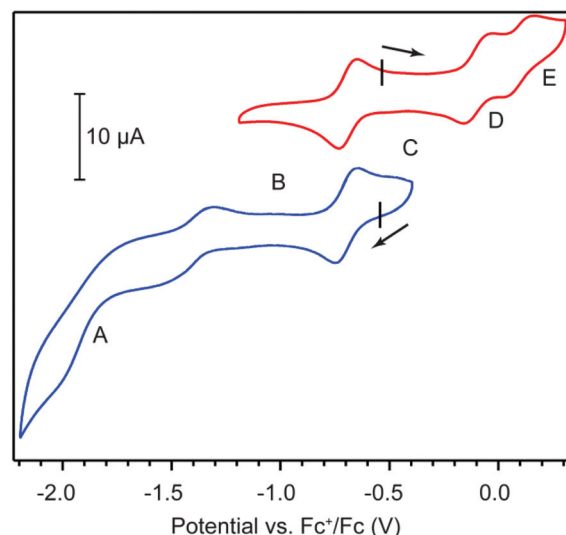


Fig. 2 Cyclic voltammograms of **1** in a 0.15 M solution of TBAPF_6 in THF under N_2 . Black tick marks indicate open circuit potentials. A, B, C, D, and E mark, respectively, the dominant species within the $[\text{Ni}_3(\text{HITP}^{n-})]$ series ($n = 5, 4, 3, 2, 1$).

between $\text{HITP}^{4-/-5-}$ and $\text{HITP}^{3-/-4-}$ corresponds to a comproportionation constant (K_c) of $10^{12.2}$.²⁷ This large value indicates full delocalization among the three phenylenediamine/BQDI arms of the HITP ligand. Additionally, K_c values of $10^{10.1}$ and $10^{3.2}$ between the $\text{HITP}^{3-/-4-}/\text{HITP}^{2-/-3-}$ and $\text{HITP}^{2-/-3-}/\text{HITP}^{-/2-}$ redox couples evidence less delocalization for the more oxidized HITP forms, suggesting that the middle oxidation state, HITP^{3-} , is the more intriguing candidate for exploring magnetic interactions mediated by HITP.

Electron paramagnetic resonance (EPR) spectroscopy provided critical evidence for assigning the spin states in **1**. X-band measurement of a frozen glass of **1** in toluene in the range 5–160 K reveals an axial pattern typical for an $S = 1/2$ spin with $g \sim 2.26$, suggesting a thermally-isolated spin state with significant Ni^{2+} character (Fig. S3a†). The absence of signals with $g \geq 4$ suggests the absence of $S > 1/2$ excited states. Because Ni^{2+} possess integer spins (either $S = 1$ or 0), the observation of a half-integer spin state in **1** suggests the presence of a HITP-centered monoradical.

An estimation of the strength of magnetic coupling within **1** came from magnetometry. Variable-field magnetization measurements at 1.8 K reveal gradual increase of the magnetization to $1.83\mu_B$ upon increasing the field to 90 kOe (Fig. 3a). This magnetization value is much higher than the value expected for an $S = 1/2$ spin ($1.0\mu_B$ with $g = 2.0$). The absence of a saturation plateau at high magnetic field or an inflection point are often associated with the presence of zero-field splitting. The temperature-dependent susceptibility data, $\chi_M T$, at 1 and 10 kOe are superimposable (Fig. S4†), confirming the absence of ferromagnetic impurities. They reveal a gradual decrease from 300 K to 30 K, followed by a steeper drop down to 1.8 K, often also associated with zero-field splitting (Fig. 3b). The $\chi_M T$ value of $0.52 \text{ cm}^3 \text{ K mol}^{-1}$ at 1.8 K is close to



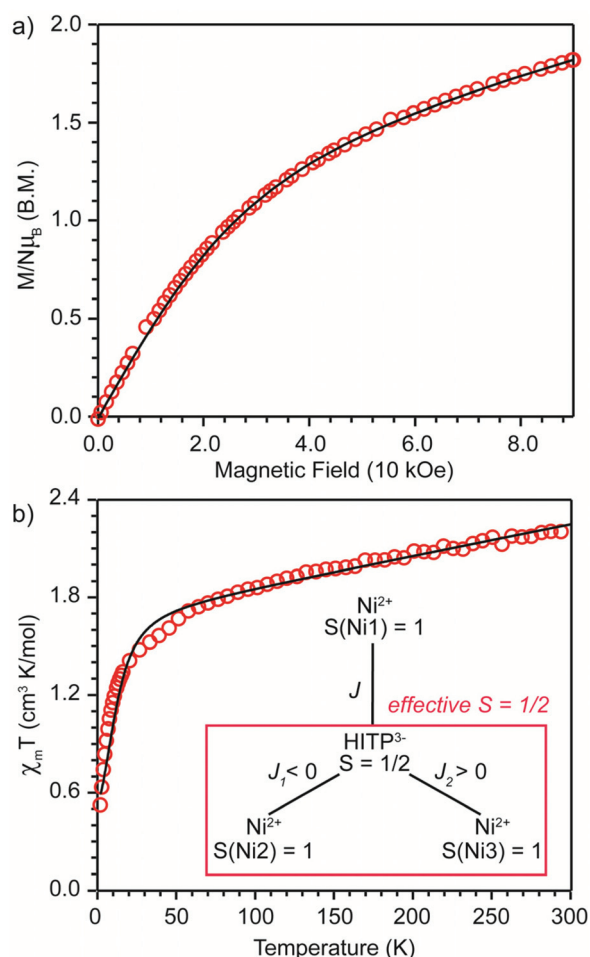


Fig. 3 (a) Field-dependent magnetization ($T = 1.8$ K); (b) temperature-dependent $\chi_M T$ ($H = 1.0$ kOe) curves for **1**. Solid black lines are fits described in text. Inset: magnetic coupling scheme proposed for **1**. The red box highlights two Ni atoms and the HITP ligand forming a single spin system with effective $S = 1/2$.

the value expected for an $S = 1/2$ spin with $g = 2.26$ ($0.48 \text{ cm}^3 \text{ K mol}^{-1}$), corroborating the ground state spin assignment based on EPR. Meanwhile, a $\chi_M T$ value of $2.21 \text{ cm}^3 \text{ K mol}^{-1}$ at 300 K is much smaller than the value expected for three uncoupled $S = 1$ Ni^{2+} centers and an $S = 1/2$ ligand ($3.375 \text{ cm}^3 \text{ K mol}^{-1}$ with $g = 2.0$). Instead, it is closer to the value of $1.76 \text{ cm}^3 \text{ K mol}^{-1}$ expected for a two-spin system comprising an $S = 1$ spin center and an $S = 1/2$ center with $g = 2.26$. In **1**, such a two-spin system could arise if we consider strong magnetic exchanges between two of the three Ni^{2+} centers and the HITP-centered radical (denoted as Ni-HITP-Ni), together forming a single $S = 1/2$ effective spin center, which itself then couples to the third Ni^{2+} center with $S = 1$. With this proposed effective two-spin model, the magnetic data for **1** can be fitted to the following Hamiltonian:

$$\mathcal{H}_1 = g_{\text{eff}} \mu_B B S_{\text{eff}} + g_{\text{Ni}_1} \mu_B B S_{\text{Ni}_1} - 2J_{\text{eff}} S_{\text{Ni}_1} + S_{\text{Ni}_1} D S_{\text{Ni}_1}$$

where S_{eff} and S_{Ni} represent the collective $S = 1/2$ spin system described above and the third $S = 1$ Ni^{2+} center. Good fits are

obtained with $g_{\text{eff}} = 2.16$, $g_{\text{Ni}_1} = 2.21$, $J = -0.79 \pm 0.01 \text{ cm}^{-1}$, $|D| = 30.2 \pm 0.1 \text{ cm}^{-1}$, $\chi_{\text{TIP}} = 1.94 \pm 0.05 \times 10^{-3} \text{ cm}^3 \text{ mol}^{-1}$, and a modest intermolecular coupling $zJ = +0.19 \pm 0.01 \text{ cm}^{-1}$ (see Fig. S5† and related discussion on zJ). These g , J , and $|D|$ values further allow satisfactory fit to the EPR data as well (Fig. S3b†). Meanwhile, two possibilities still remain for the effective $S = 1/2$ spin centered on Ni-HITP-Ni, with $S(\text{Ni}_2) = S(\text{Ni}_3)$ equal to either 1 or 0. As will be discussed below, broken-symmetry density functional theory (BS-DFT) calculations suggest that $S(\text{Ni}_2) = S(\text{Ni}_3) = 1$ is the more appropriate representation for **1**. Specifically, both strong antiferromagnetic (J_1) and ferromagnetic (J_2) exchange interactions persist at room temperature between independent Ni-HITP pairs, and can be described by incorporating the term $-2J_1 S_{\text{Ni}_2} S_{\text{HITP}} - 2J_2 S_{\text{Ni}_3} S_{\text{HITP}}$ into \mathcal{H}_1 (Fig. 3b inset). Although the weak temperature dependence of $\chi_M T$ above 30 K precludes accurate determination of J_1 and J_2 , lower bounds can be estimated under the assumption $|J_1| = |J_2|$, suggesting $-J_1 = J_2 \geq 1300 \text{ cm}^{-1}$ (Fig. S6†). We note that these values should only serve as estimates, because the slope in the high-temperature region of $\chi_M T$ is sensitive to subtle changes in diamagnetic corrections.¹¹ Nevertheless, the large estimates for $J_{1,2}$ confirm that the tritopic radical bridge enables strong magnetic exchange interactions that persist at room temperature. Alternative spin models did not provide satisfactory fits (see discussion on page 12 in the ESI†).

BS-DFT analysis provided additional insight into the magnetic interactions in **1**. Electronic and spin ground states of **1** were evaluated by comparing the single-point energy of the states with $S = 1$ (termed “BS state”) or $S = 0$ (termed “diamagnetic-Ni state”) for the two Ni atoms in the Ni-HITP-Ni moiety (Fig. 3b and S7a†). The calculation revealed the BS state lying 1524.8 cm^{-1} below the diamagnetic-Ni state, supporting the assignment of all Ni^{2+} having $S = 1$ spin state in **1** (Fig. 4 and S7b†). Moreover, Löwdin spin density analysis for the BS state showed dominant positive spin density on two of the three Ni atoms, and negative density on HITP and the third Ni, con-

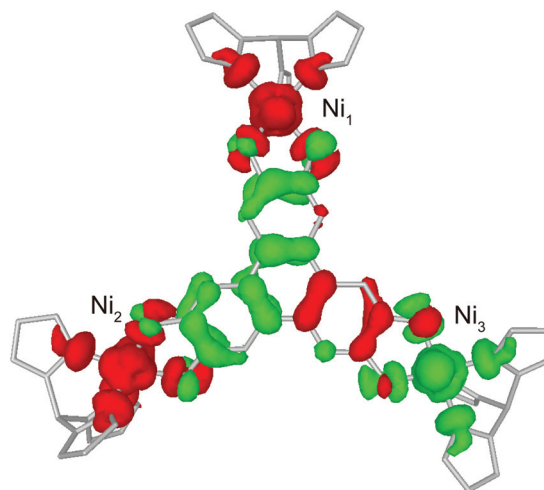


Fig. 4 Calculated spin density isosurfaces (0.0015 a.u.) in the broken-symmetry state of **1**. Red and green represent positive and negative spin densities. Labels for Ni are consistent with Fig. 3.

There are no conflicts to declare.

- 1 P. Dechambenoit and J. R. Long, *Chem. Soc. Rev.*, 2011, **40**, 3249.
- 2 G. Mínguez Espallargas and E. Coronado, *Chem. Soc. Rev.*, 2018, **47**, 533–557.
- 3 A. E. Thorarinsdottir and T. D. Harris, *Chem. Rev.*, 2020, **120**, 8716–8789.
- 4 N. Motokawa, S. Matsunaga, S. Takaishi, H. Miyasaka, M. Yamashita and K. R. Dunbar, *J. Am. Chem. Soc.*, 2010, **132**, 11943–11951.
- 5 J. Zhang, W. Kosaka, K. Sugimoto and H. Miyasaka, *J. Am. Chem. Soc.*, 2018, **140**, 5644–5652.
- 6 S. Demir, I. R. Jeon, J. R. Long and T. D. Harris, *Coord. Chem. Rev.*, 2015, **289–290**, 149–176.
- 7 M. Atzori and R. Sessoli, *J. Am. Chem. Soc.*, 2019, **141**, 11339–11352.
- 8 A. Caneschi, D. Gatteschi, R. Sessoli and P. Rey, *Acc. Chem. Res.*, 1989, **22**, 392–398.
- 9 C. Benelli, A. Dei, D. Gatteschi and L. Pardi, *Inorg. Chem.*, 1988, **27**, 2831–2836.
- 10 V. I. Ovcharenko, E. V. Gorelik, S. V. Fokin, G. V. Romanenko, V. N. Ikorskii, A. V. Krashilina, V. K. Cherkasov and G. A. Abakumov, *J. Am. Chem. Soc.*, 2007, **129**, 10512–10521.
- 11 I.-R. Jeon, J. G. Park, D. J. Xiao and T. D. Harris, *J. Am. Chem. Soc.*, 2013, **135**, 16845–16848.
- 12 K. Chłopek, E. Bothe, F. Neese, T. Weyhermüller and K. Wieghardt, *Inorg. Chem.*, 2006, **45**, 6298–6307.
- 13 N. Mavragani, D. Errulat, D. A. Gálico, A. A. Kitos, A. Mansikkamäki and M. Murugesu, *Angew. Chem., Int. Ed.*, 2021, DOI: [10.1002/anie.202110813](https://doi.org/10.1002/anie.202110813).
- 14 C. A. Gould, L. E. Darago, M. I. Gonzalez, S. Demir and J. R. Long, *Angew. Chem., Int. Ed.*, 2017, **56**, 10103–10107.
- 15 A. Dacu, N. Roques, V. Jubera, D. Maspoch, X. Fontrodona, K. Wurst, I. Imaz, G. Mouchaham, J.-P. Sutter, C. Rovira and J. Veciana, *Chem. – Eur. J.*, 2012, **18**, 152–162.
- 16 J. O. Moilanen, N. F. Chilton, B. M. Day, T. Pugh and R. A. Layfield, *Angew. Chem., Int. Ed.*, 2016, **55**, 5521–5525.
- 17 R. Breslow, B. Jaun, R. Q. Kluttz and C. Xia, *Tetrahedron*, 1982, **38**, 863–867.
- 18 Y. Wang, F. Lambert, E. Rivière, R. Guillot, C. Herrero, A. Tissot, Z. Halime and T. Mallah, *Chem. Commun.*, 2019, **55**, 12336–12339.
- 19 L. Yang and M. Dincă, *Angew. Chem., Int. Ed.*, 2021, **60**, 23784–23789.

- 20 J. Cirera, E. Ruiz and S. Alvarez, *Organometallics*, 2005, **24**, 1556–1562.
- 21 D. J. Harding, P. Harding, H. Adams and T. Tuntulani, *Inorg. Chim. Acta*, 2007, **360**, 3335–3340.
- 22 S. Pascal and O. Siri, *Coord. Chem. Rev.*, 2017, **350**, 178–195.
- 23 F. Zhong, X. Yang, L. Shen, Y. Zhao, H. Ma, B. Wu and X. J. Yang, *Inorg. Chem.*, 2016, **55**, 9112–9120.
- 24 L. Yang, X. He and M. Dincă, *J. Am. Chem. Soc.*, 2019, **141**, 10475–10480.
- 25 T. Kato and T. Yamabe, *Chem. Phys. Lett.*, 2005, **403**, 113–118.
- 26 N. Hoshino and T. Akutagawa, *Chem. – Eur. J.*, 2018, **24**, 19323–19331.
- 27 D. E. Richardson and H. Taube, *Coord. Chem. Rev.*, 1984, **60**, 107–129.
- 28 T. Glaser, M. Heidemeier, J. B. H. Strautmann, H. Bögge, A. Stämmler, E. Krickemeyer, R. Huenerbein, S. Grimme, E. Bothe and E. Bill, *Chem. – Eur. J.*, 2007, **13**, 9191–9206.
- 29 K. Chłopek, E. Bothe, F. Neese, T. Weyhermüller and K. Wieghardt, *Inorg. Chem.*, 2006, **45**, 6298–6307.
- 30 D. Schweinfurth, M. M. Khusniyarov, D. Bubrin, S. Hohloch, C.-Y. Su and B. Sarkar, *Inorg. Chem.*, 2013, **52**, 10332–10339.

