




Highlighting research from Dr Hatice Mutlu and co-workers within the Soft Matter Synthesis Laboratory at Karlsruhe Institute of Technology, Germany.

Straightforward synthesis of aliphatic polydithiocarbonates from commercially available starting materials

A facile synthetic strategy towards functional and structurally diverse polydithiocarbonates, which reveal unexplored intrinsic emission properties, was developed under benign and mild reaction conditions by taking advantage of the versatile reactivity of 1,1'-carbonyldiimidazole (CDI) with dithiols in the presence of diazabicyclo[5.4.0]undec-7-ene (DBU), as an efficient base.

As featured in:

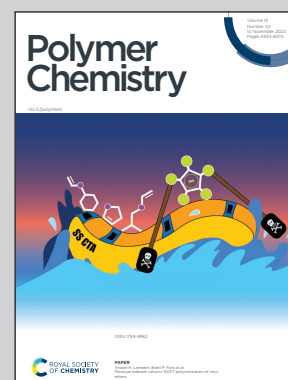

See Hatice Mutlu *et al.*,
Polym. Chem., 2022, **13**, 5965.



Cite this: *Polym. Chem.*, 2022, **13**, 5965

Received 27th July 2022,
Accepted 26th September 2022

DOI: 10.1039/d2py00990k

rsc.li/polymers

Straightforward synthesis of aliphatic polydithiocarbonates from commercially available starting materials†

Timo Sehn, Birgit Huber, Julian Fanelli and Hatice Mutlu *

Herein, a novel 1,1'-carbonyldiimidazole (CDI) mediated polymerization methodology that complements ROP and unlocks a greater synthetic window to less-recognized polydithiocarbonates is presented.

Sulfur containing polymers^{1,2} are fascinating macromolecules that have received increasing attention due to their unique properties (*e.g.*, affinity to metals, improved refractive index, divergent redox and thermal characteristics, and enhanced chemical and biological properties). As a matter of fact, sulfur tethered macromolecules [particularly, polythiocarbonates, polydithiocarbonates (depicted in Scheme 1A) and polytrithiocarbonates] show higher susceptibility to light induced degradation (although they are recognized to be non-biodegradable),^{3,4} compared to their oxygen counterparts (*i.e.*, polycarbonates). In this way, those polymers could even facilitate new light-induced chemical recycling methods as an answer to the ever-increasing amount of plastic pollution.⁵ Indeed, several (degradable) polymeric scaffolds decorated with various sulfur-functionalities (*e.g.*, thioethers, thioesters, thiocarbonates, thiourethanes, thioamides, and thioureas among others) are now accessible.¹ Still, compared to the more conventional oxygen-rich polymers (such as aliphatic polycarbonates),⁶ the toolbox of polymerizations to furnish sulfur-rich polymers (particularly, aliphatic polydithiocarbonates in which both of the ethereal oxygen atoms of the carbonate group are replaced by sulfur atoms) remains limited to polycondensation (Scheme 1B)⁷ and the ring-opening polymerization (ROP) of cyclic sulfur-containing monomers (Scheme 1C).⁸ The mentioned approaches are usually accompanied by unavoidable drawbacks involving the usage of toxic phosgene (or chloroformates) along with the tedious and low yield multiple synthetic steps of the cyclic monomers.

Indeed, the absence of practical synthetic strategies that unlock a greater number of functional aliphatic polydithiocarbonates has most likely inhibited their broader use in appli-



Scheme 1 Schematic representation of: (A) the replacement of oxygen with sulfur atoms in polycarbonates, resulting in polydithiocarbonates; previously reported approaches for polydithiocarbonate synthesis: (B) phosgene-based step-growth and (C) ring-opening polymerizations; (D) The reactivity of CDI with diverse nucleophiles; (E) the currently investigated CDI mediated polymerization for polydithiocarbonate synthesis in the presence of DBU.

Soft Matter Synthesis Laboratory, Karlsruhe Institute of Technology (KIT), Hermann-von-Helmholtz-Platz 1, D-76344 Eggenstein-Leopoldshafen, Germany.

E-mail: hatice.mutlu@kit.edu

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2py00990k>



cation-driven research. Although, aliphatic polydithiocarbonates could offer parallel properties and applications to those of the corresponding polycarbonates.

Aliphatic polydithiocarbonates, as analogues of polycarbonates, are expected to have improved thermal properties. In fact, a literature survey reveals^{7,9–11} that higher melting temperatures have been reported for aliphatic polydithiocarbonates with respect to the oxygenated analogues.^{12,13} Thus, in particular, poly(hexamethylene dithiocarbonate) has a melting temperature (T_m) about 60 °C higher than that of poly(hexamethylene carbonate), *i.e.*, 90 °C *vs.* 30 °C.¹⁰ The latter behaviour could be attributed to the higher packing efficiency in the crystalline lattice when sulfur atoms are present in the polymer backbone.¹⁴ In other words, poly(hexamethylene dithiocarbonate) is a material with a higher degree of crystallinity compared to poly(hexamethylene carbonate), respectively about 60% *vs.* 15%, and thus, reflects a faster crystallisation rate. Moreover, polymer chains decorated with –S–CO–S– groups are known to show higher flexibility and mobility compared to the chains containing –O–CO–O– groups.

Besides, the poly(hexamethylene dithiocarbonate) derivative shows a decomposition temperature (T_d) of ~320 °C (as it is discussed below) which is 40 °C higher compared to the oxygen analogue (~280 °C).¹⁵

1,1'-Carbonyldiimidazole (CDI, also known as Staab's reagent)¹⁶ has been employed for various applications in organic chemistry,^{17,18} and quite recently for polymer synthesis by virtue of its reactivity with various nucleophiles (carboxylic acids, alcohols, and amines) as shown in Scheme 1D.^{19,20}

Moreover, CDI is safe, cheap (3 € per gram), and easy to handle, compared to the commonly used toxic phosgene or chloroformates. In fact, Malkoch²⁰ and colleagues reported the detailed phosgene-free synthesis of aliphatic polycarbonates with a broad range of properties. Surprisingly, literature survey has revealed that the synthesis of polydithiocarbonates in the presence of CDI is so far an unexplored research ground (Scheme 1E), despite the obvious advantages including easily available monomers (dithiols, which possess higher nucleophilicity compared to diols) and the relatively low toxicity of the imidazole by-product. Accordingly, the continuously increasing need for advanced materials prompted us to investigate a new synthetic approach with emphasis on operational practicality. In other words, we herein disclose a novel synthetic strategy that expands the window of aliphatic polydithiocarbonates that are synthesized from simple dithiol building blocks in the presence of a slight excess of CDI (*i.e.*, 1.05 equiv.). In fact, the main idea of utilizing the slight excess of CDI is to achieve tailor-made imidazole end-groups, which subsequently could be easily transformed into the corresponding methyl monothiocarbonate end-groups during the precipitation process in ice-cold methanol (the mechanism of the polymerization is depicted in Scheme S1†). In this way we ensure that no free-thiol end groups are present, which could give rise to polydisulfide formation. Given the fact that diazabicyclo[5.4.0]undec-7-ene (DBU) has been recognized as an effective organocatalyst for the CDI-mediated²¹ nucleophilic

reactions as well as in a variety of thiol-based²² organic syntheses, we sought to examine the effect of DBU on the polymerization. Within the broad family of aliphatic polydithiocarbonates, the synthesis of poly(hexamethylene dithiocarbonate) is the most widely explored as this polymer distinguishes itself by virtue of its complex thermal behaviour.¹⁰ Hence, to prove our hypothesis as a suitable strategy, an initial screening of the reaction conditions was performed using 1,6-hexane dithiol **M1** (shown in Fig. 1A) and CDI (Scheme 1E and Table S1†) in the presence of different equivalents of DBU (Fig. S1†) in 0.8 M chloroform to deliver polymer **P1**. In particular, by screening 2.00, 0.10 and 0.01 equivalents of DBU, the contribution of the base to the reaction and its impact on the degree of polymerization were investigated. Indeed, the efficiency of the base could be confirmed by using 2.00 equivalents of DBU resulting in polymer **P1** with an apparent number average molecular weight (M_n) of 11 500 g mol⁻¹ and dispersity (D) of 2.1 in 4 hours at ambient temperature (Fig. 1B). Notably, the reaction was also effective using lower loadings of DBU (0.01 equivalent), however resulting in a lower M_n . The polymerization reaction which was carried out with no base (**P1.3** in Table S1†) showed that only a very low molecular weight polymer was formed regardless of the reaction time. These results underpin the non-catalytic nature of the base in this reaction. It is assumed that DBU is removed from the reaction mixture by scavenging the formed by-product imidazole to yield an ionic liquid (compare Scheme S1†),²³ thus reducing the concentration of the active base in the reaction solution. Nevertheless, the formation of an ionic liquid (IL) could be beneficial for the synthesis of the targeted polydithiocarbonates, as it has been recently reported that ionic liquids (ILs) can pave the way towards an eco-compatible route for synthesizing polycarbonates from sterically hindered alcohol derivatives (*i.e.*, isosorbide) and dimethyl carbonate.²⁴ The authors clearly emphasized that the cation and anion of ILs should synergistically activate the substrates. Indeed, the formation of the ionic liquid was also clearly observed with the aid of NMR analysis (particularly ¹³C NMR), which was performed on the crude reaction mixture after 2 hours of the polymerization to deliver **P1** (Fig. S2 in the ESI†). The respective NMR data were compared with the ¹³C NMR spectrum of the freshly prepared DBU–imidazole ionic liquid mixture in addition to the NMR data of pure DBU and pure imidazole (all data were collected in CDCl₃). Accordingly, a magnetic resonance at 162.4 ppm (compare Fig. S2†) that can be assigned to the protonated DBU species (DBUH⁺) of the formed ionic liquid (which is consistent with the literature value, *i.e.*, 162.1 ppm)²⁵ was detected. Although, the literature survey²⁴ has emphasized that the cation and anion of ILs could synergistically activate the polymerization reaction, the stoichiometric ratio of DBU was increased, yielding the highest molecular weights, when 2.00 equiv. were employed. Crucially, the beneficial features of CDI include its low nucleophilicity and distinct neutral character, enabling the effective formation of polydithiocarbonates without the need for the continuous removal of the imidazole by-product (without the need for any additional setup).





Fig. 1 (A) Chemical structures of monomers **M1** and **M2** in addition to the synthesized (co)polymers **P1–P4**. (B) SEC traces of step growth polymers **P1** ($M_n = 11\,500\text{ g mol}^{-1}$, $D = 2.1$, black line), **P2** ($M_n = 14\,700\text{ g mol}^{-1}$, $D = 2.4$, red line), **P3** ($M_n = 14\,000\text{ g mol}^{-1}$, $D = 2.1$, blue line) and **P4** ($M_n = 6500\text{ g mol}^{-1}$, $D = 2.5$, green line) in THF + 0.2% w/v BHT. (C) ¹H NMR spectra (400 MHz, CDCl₃, 298 K) of CDI (up, blue line), **M1** (middle, red line) and **P1** (bottom, black line). (D) ATR-IR spectra of CDI (green line), **M1** (blue line), **P1** (red line) and **P4** (black line).

The polymerization of **P1** was monitored by Size Exclusion Chromatography (SEC) of reaction aliquots withdrawn at 30, 90, 120 and 240 min. In fact, the results depicted in Fig. S3† together with the mechanism postulated in Scheme S1† suggest a step-growth polymerization mechanism. Nevertheless, further studies (which are currently performed in our laboratories) are necessary in order to conclude the latter statement.

The successful incorporation of dithiocarbonate units into the polymer backbone was further demonstrated by NMR (1D and 2D), ATR-IR and UV-Vis analyses. The ¹H NMR spectrum and peak assignments of **P1** are shown in Fig. 1C, where explicitly the appearance of magnetic resonance corresponding to the -CH₂- groups at the α-position to the dithiocarbonate, *i.e.*, at 2.97 ppm, was observed. Moreover, the complete disappearance of the magnetic resonances of terminal -SH at 1.33 ppm and imidazole protons (appearing from 7.11 to 8.19 ppm) also confirmed the successful polymerization. In a complementary way, a new magnetic resonance that arose at

190 ppm was detected in ¹³C NMR (Fig. S4†), attributable to the carbonyl carbon of the dithiocarbonate moiety in **P1** (which is also consistent with the literature).²⁶ Furthermore, 2D NMR, *i.e.* ¹H-¹H correlation spectroscopy (COSY) and heteronuclear single quantum coherence (HSQC) spectroscopy (Fig. S5 and S6 in the ESI†), confirmed in a supplementary manner the formation of the targeted polymer structure. Besides, the attenuated total reflectance infrared (ATR-IR) spectrum of **P1** shown in Fig. 1D revealed the characteristic C=O stretching vibration band of dithiocarbonate moieties at ~1635 cm⁻¹, while neither the =C-H stretch vibration band of imidazole nor the S-H stretch vibration band of thiol groups could be observed (appearing in the ranges of 3000 to 3150 cm⁻¹ and 2550 to 2598 cm⁻¹, respectively). Moreover, a band at 871 cm⁻¹ due to the C-S stretching was also detectable. Importantly, NMR and ATR-IR analyses affirmed that the resulting polymers contain only the expected polydithiocarbonate segments. Neither polydisulfide and polymonothiocarbo-



try (DSC). On the one hand, the decomposition temperature (T_d), defined as the temperature at which 5% weight loss takes place, was observed for **P1** at 321 °C (Fig. 3A), because of the

highly crystalline behaviour. On the other hand, **P2–P4** showed lower thermal stability, *i.e.*, 258 °C < T_d < 280 °C. Importantly, all (co)polymers displayed a single step thermal degradation



Fig. 3 (A) Thermogravimetric analysis (TGA) of **P1** (black line), **P2** (red line), **P3** (blue line) and **P4** (green line) from 25 to 800 °C with a heating rate of 10 K min⁻¹ under a nitrogen flow. (B) Differential scanning calorimetry (DSC) studies (second heating run) of **P1** (black line), **P2** (red line), **P3** (blue line) and **P4** (green line) from -80 °C to 200 °C with a heating rate of 10 K min⁻¹ under a nitrogen flow (as for **P1**, measurement was from -40 °C). (C) Absorption traces of **P2** at different concentrations (black: 0.002 mg mL⁻¹, red: 0.006 mg mL⁻¹, blue: 0.016 mg mL⁻¹ and green: 0.050 mg mL⁻¹) in DCM (298 K). (D) Emission spectra of **P2** at various excitation wavelengths (from 310 nm to 430 nm) in DCM ($c = 39.5$ mg mL⁻¹). (E) Emission spectra of **P2** at different concentrations (black: 1.00 mg mL⁻¹, red: 5.66 mg mL⁻¹, blue: 13.3 mg mL⁻¹ and green: 39.5 mg mL⁻¹) in DCM (298 K) at $\lambda_{exc} = 340$ nm. (F) Emission spectra of **P2** in DCM/water mixtures with an increasing water ratio (black: 5%, red: 10%, blue: 15% and green: 20%) at 298 K; the arrow indicates the slight shift of the maxima of each emission spectrum.



sion intensity of the corresponding polymer solution increased with elevated water fractions according to the typical aggregation-enhanced emission (AEE) effect (Fig. 3F).⁴⁸ The maximum fluorescence emission intensity of the polymer solution of **P2** was achieved with a water fraction of 15%. However, when the water fraction reached 20%, the polymer, *i.e.*, **P2**, precipitated, and the mixture started to become opaque. Consequently, the fluorescence emission intensity of the polymer solution faded at a water content of 20%. Hence, the experiment revealed in a different way that the macromolecular mechanics, *i.e.*, AEE effect, gives rise to the unexpected fluorescence character of the aliphatic polydithiocarbonates, specifically **P2** in our case.

Last but not least, in order to validate the abovementioned results and get more insights into the emission mechanism, a model compound, **MC**, mimicking the repeating unit of **P2** (Fig. 4A) was synthesized (Sections B6 and B7, and Fig. S25–S28 in the ESI†). The respective absorbance and emission data of this compound in DCM were recorded and compared with the optical properties of the starting compound 3,6-dioxa-1,8-octanedithiol in addition to the intermediate product 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole (Fig. 4B and C). The spectral patterns of these compounds (particularly, 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole and **MC** at 10 mg mL⁻¹) were similar to each other with a strong absorption band around 284 nm (with an obvious red-shift of 50 nm in comparison with that of 3,6-dioxa-1,8-octanedithiol)

suggesting increased intramolecular cluster triggered interaction plausibly owing to the clusterization of the dithiocarbonyl moiety. Moreover, a shoulder around 370 nm was observed for 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole as a result of the $n-\pi^*$ electron transitions of the imidazole moieties.⁵¹ Meanwhile, as a maximum emission wavelength of 423 nm was detected at $\lambda_{\text{exc}} = 340$ nm for **P2**, 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole and **MC** were subjected to analogue analysis; a slightly lower maximum emission wavelength of 351 nm was recorded at $\lambda_{\text{exc}} = 340$ nm. The intensity of 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole was slightly higher in comparison with that of **MC** (185 vs. 140 a.u.), which can be attributed to the presence of the imidazole and thio-urethane units. In contrast, no emission was observed for 3,6-dioxa-1,8-octanedithiol. In a similar manner to **P2**, a significant increase of the fluorescence emission intensity was observed for **MC** while increasing the compound concentration from 1.00 mg mL⁻¹ to 50 mg mL⁻¹ (Fig. 4D). The slight red shift of the emission band located at 404 (5.00 mg mL⁻¹) nm to a slightly higher wavelength of 412 nm (50 mg mL⁻¹) was also in accordance with the results observed for **P2**.

On the one hand, these results may show that the dithiocarbonate unit could be both a CTEgen and an AIEgen, demonstrating the important role of clusterization in the manipulation of the photophysical behaviour of a molecular unit either in solution or in an aggregated state. On the other hand, to further



Fig. 4 (A) The synthesis of a model compound, **MC**, mimicking the repeating unit of **P2**. (B) Absorption traces of **MC**, 3,6-dioxa-1,8-octanedithiol and the intermediate product 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole in DCM (298 K). (C) Emission spectra of **MC**, 3,6-dioxa-1,8-octanedithiol and the intermediate product 3,6-dioxa-1,8-octanedithio-*bis*-carbonylimidazole in DCM (10 mg mL⁻¹) at $\lambda_{\text{exc}} = 340$ nm. (D) Emission spectra of **MC** at different concentrations (from 1.00 mg mL⁻¹ to 50.0 mg mL⁻¹) in DCM (298 K) at $\lambda_{\text{exc}} = 340$.



understand the fluorescence behaviour of those classes of polymers and the respective small molecules at the molecular level, density functional theory (DFT) calculations are essential.

Conclusions

In conclusion, we have presented a facile synthetic strategy to obtain polydithiocarbonates (particularly poly(hexamethylene dithiocarbonate) and its copolymers) under benign and mild reaction conditions by taking advantage of the versatile reactivity of 1,1'-carbonyldiimidazole, CDI, with dithiols in the presence of diazabicyclo[5.4.0]undec-7-ene, DBU, as an efficient base. Crucially, the beneficial features of CDI include its low nucleophilicity and distinct neutral character, enabling the effective formation of polydithiocarbonates without the need for continuous removal of the imidazole by-product. The polymerization followed a traditional step-growth mechanism which was favored over depolymerization, and it is postulated that this approach should serve as a complement to the existing methodologies by combining the operational benefits of the ROP and scalability of traditional step-growth polymerization protocols. Indeed, the methodology facilitates the fabrication of previously inaccessible functionally and structurally diverse dithiocarbonate-decorated macromolecules, which exhibit unexplored photophysical properties. It is important to mention that studies on the degradation properties of those polymers are currently investigated. Thus, we truly believe that this approach will play a crucial role in the future availability of advanced polydithiocarbonates, and their use as materials in the technical and biomedical engineering fields, particularly on account of their unexplored intrinsic emission properties (which still need to be investigated in detail).

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

H. M. acknowledges the continuous financial support from the Karlsruhe Institute of Technology, in addition to the Federal Ministry of Education and Research (BMBF) and the Baden-Württemberg Ministry of Science as part of the Excellence Strategy of the German Federal and State Governments. Prof. M. A. R. Meier and Prof. P. Levkin, respectively, are acknowledged for the access of diverse analytical characterization facilities. Prof. P. Theato is acknowledged for his continuous support and access of the SML facilities.

References

- H. Mutlu, E. B. Ceper, X. Li, J. Yang, W. Dong, M. M. Ozmen and P. Theato, *Macromol. Rapid Commun.*, 2019, **40**, 1800650.
- H. Mutlu and P. Theato, *Macromol. Rapid Commun.*, 2020, **41**, 2000181.
- B. A. Fultz, D. Beery, B. M. Coia, K. Hanson and J. G. Kennemur, *Polym. Chem.*, 2020, **11**, 5962.
- T. M. McGuire and A. Buchard, *Polym. Chem.*, 2021, **12**, 4253.
- T.-J. Yue, L.-Y. Wang and W.-M. Ren, *Polym. Chem.*, 2021, **12**, 6650.
- E. A. Gilbert, M. L. Polo, J. M. Maffi, J. F. Guastavino, S. E. Vaillard and D. A. Estenoz, *J. Polym. Sci.*, 2022, DOI: [10.1002/pol.20220119](https://doi.org/10.1002/pol.20220119).
- G. Montaudo, C. Puglisi, C. Berti, E. Marianucci and F. Pilati, *J. Polym. Sci., Part A: Polym. Chem.*, 1989, **27**, 2277.
- S. Krishnamurthy, Y. Yoshida and T. Endo, *Polym. Chem.*, 2022, **13**, 267.
- F. Pilati, E. Marianucci, C. Berti, P. Manaresi and G. D. Fortuna, *Polym. Commun.*, 1990, **31**, 431.
- C. Berti, A. Celli, P. Marchese, E. Marianucci, C. Marega, V. Causin and A. Marigo, *Polymer*, 2007, **48**, 174.
- T. P. Zhao, A. Celli, X. K. Ren, J. R. Xu, S. Yang, C. Y. Liu and E. Q. Chen, *Polymer*, 2017, **113**, 267.
- H. R. Kricheldorf and A. Mahler, *Polymer*, 1996, **37**, 4383.
- V. Pokharkar and S. Sivaram, *Polymer*, 1995, **36**, 485.
- E. Riande, J. Guzman and J. S. Roman, *J. Chem. Phys.*, 1980, **72**, 5263.
- W. Liu, W. Zhu, C. Li, G. Guan, D. Zhang, Y. Xiao and L. Zheng, *Polym. Degrad. Stab.*, 2015, **112**, 70.
- H. A. Staab, *Justus Liebigs Ann. Chem.*, 1957, **609**, 75.
- R. Paul and G. W. Anderson, *J. Am. Chem. Soc.*, 1960, **82**, 4596.
- S. P. Rannard and N. J. Davis, *Org. Lett.*, 1999, **1**, 933.
- J. D. Wolfgang, B. T. White and T. E. Long, *Macromol. Rapid Commun.*, 2021, **42**, 2100163.
- J. V. Olsson, D. Hult, S. García-Gallego and M. Malkoch, *Chem. Sci.*, 2017, **8**, 4853.
- C. Larrivé-Aboussafy, B. P. Jones, K. E. Price, M. A. Hardink, R. W. McLaughlin, B. M. Lillie, J. M. Hawkins and R. Vaidyanathan, *Org. Lett.*, 2010, **12**, 324.
- Y. H. Wang, Z. Y. Cao, Q. H. Li, G. Q. Lin, J. Zhou and P. Tian, *Angew. Chem.*, 2020, **132**, 8080.
- Z. Li, DBU-Based Ionic Liquids, in *Encyclopedia of Ionic Liquids*, ed. S. Zhang, Springer, Singapore, 2022. DOI: [10.1007/978-981-10-6739-6_126-1](https://doi.org/10.1007/978-981-10-6739-6_126-1).
- W. Qian, X. Ma, L. Liu, L. Deng, Q. Su, R. Bai, Z. Zhang, H. Gou, L. Dong, W. Cheng and F. Xu, *Green Chem.*, 2020, **22**, 5357.
- F. Gao, Z. Wang, P. Ji and J.-P. Cheng, *Front. Chem.*, 2019, **6**, 658.
- X.-H. Zhang, F. Liu, X.-K. Sun, S. Chen, B.-Y. Du, G.-R. Qi and K. M. Wan, *Macromolecules*, 2008, **41**, 1587.
- Y. Hu, Z. Yin, T. Werner, A. Spannenberg and X.-F. Wu, *Eur. J. Org. Chem.*, 2018, 1274.
- R. Steudel, *Angew. Chem., Int. Ed. Engl.*, 1975, **14**, 655.
- R. M. Fitch and D. C. Helgeson, *J. Polym. Sci., Polym. Symp.*, 1969, **22**, 1101.
- Q. Zhou, B. Cao, C. Zhu, S. Xu, Y. Gong, W. Z. Yuan and Y. Zhang, *Small*, 2016, **12**, 6586.



- 31 P. Liao, J. Huang, Y. Yan and B. Z. Tang, *Mater. Chem. Front.*, 2021, **5**, 6693.
- 32 Y. N. Hong, J. W. Y. Lam and B. Z. Tang, *Chem. Soc. Rev.*, 2011, **40**, 5361.
- 33 J. Mei, N. L. C. Leung, R. T. K. Kwok, J. W. Y. Lam and B. Z. Tang, *Chem. Rev.*, 2015, **115**, 11718.
- 34 H. K. Zhang, Z. Zhao, P. R. McGonigal, R. Q. Ye, S. J. Liu, J. W. Y. Lam, R. T. K. Kwok, W. Z. Yuan, J. P. Xie, A. L. Rogach and B. Z. Tang, *Mater. Today*, 2020, **32**, 275.
- 35 D. A. Tomalia, B. Klajnert-Maculewicz, K. A. M. Johnson, H. F. Brinkman, A. Janaszewska and D. M. Hedstrand, *Prog. Polym. Sci.*, 2019, **90**, 35.
- 36 W. Z. Yuan and Y. M. Zhang, *J. Polym. Sci. Polym. Chem.*, 2017, **55**, 560.
- 37 Y. Wang, X. Bin, X. Chen, S. Zheng, Y. Zhang and W. Z. Yuan, *Macromol. Rapid Commun.*, 2018, **39**, 1800528.
- 38 J. Yang, Y. Zhang, S. Gautam, L. Liu, J. Dey, W. Chen, R. P. Mason, C. A. Serrano, K. A. Schug and L. Tang, *Proc. Natl. Acad. Sci. U. S. A.*, 2009, **106**, 10086.
- 39 R. B. Wang, W. Z. Yuan and X. Y. Zhu, *Chin. J. Polym. Sci.*, 2015, **33**, 680.
- 40 J. Yan, B. Zheng, D. Pan, R. Yang, Y. Xu, L. Wang and M. Yang, *Polym. Chem.*, 2015, **6**, 6133.
- 41 R. B. Restani, P. I. Morgado, M. P. Ribeiro, I. J. Correia, A. Aguiar-Ricardo and V. D. B. Bonifácio, *Angew. Chem., Int. Ed.*, 2012, **51**, 5162.
- 42 X. Zhou, W. Luo, H. Nie, L. Xu, R. Hu, Z. Zhao, A. Qin and B. Z. Tang, *J. Mater. Chem. C*, 2017, **5**, 4775.
- 43 L. Yang, L. Wang, C. Cui, J. Lei and J. Zhang, *Chem. Commun.*, 2016, **52**, 615.
- 44 B. Liu, H. K. Zhang, S. J. Liu, J. Z. Sun, X. H. Zhang and B. Z. Tang, *Mater. Horiz.*, 2020, **7**, 987.
- 45 Z. Zhang, S. Feng and J. Zhang, *Macromol. Rapid Commun.*, 2016, **37**, 318.
- 46 Z. Zhao, X. Chen, Q. Wang, T. Yang, Y. Zhang and W. Z. Yuan, *Polym. Chem.*, 2019, **10**, 3639.
- 47 W. Huang, H. Yan, S. Niu, Y. Du and L. Yuan, *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 3690.
- 48 Y. Du, Y. Feng, H. Yan, W. Huang, L. Yuan and L. Bai, *J. Photochem. Photobiol., A*, 2018, **364**, 415.
- 49 Y. F. Zhang, W. M. Lai, S. Xie, H. Zhou and X. B. Lu, *Polym. Chem.*, 2022, **13**, 201.
- 50 M. W. Fichtner and N. F. Haley, *J. Org. Chem.*, 1981, **46**, 3141.
- 51 X. Lin, M. Huang, T. Lu, W. Zhao, C. Hu, X. Gu and W. Zhang, *Atmosphere*, 2022, **13**, 970.

