

EES Batteries

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: J. Wang, K. Yan, H. Qi, D. Xu, S. Guo, L. Pei, Z. Peng, D. Huang, Y. Luo and F. Cao, *EES Batteries*, 2025, DOI: 10.1039/D5EB00098J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Aqueous zinc-ion batteries (AZIBs), characterized by intrinsic safety and low cost, are highly desirable for large-scale energy storage. However, the instability of the Zn metal anode, caused by uncontrollable dendrite growth and severe hydrogen evolution reactions, limits their cycle life. To address this issue, we have designed a highly conductive zinc phosphate protective interphase with a thickness of ~ 40 nm and no direct interface with the Zn substrate, enhancing both cycling stability and high-rate capability of AZIBs. As anticipated, this thermal treatment process results in a strongly oriented Zn texture, with the (002) crystal plane predominantly aligned, due to the robust interaction between zinc phosphate and the (002) plane. Moreover, symmetric cells exhibit significantly extended cycling life, exceeding 5900 hours at 0.5 mA cm^{-2} , and over 1400 hours at an ultrahigh current density of 100 mA cm^{-2} (more than 16,000 cycles). These results underscore the considerable potential of the zinc phosphate interphase for improving the performance of AZIBs. The comprehensive performance of the P-Zn anode represents a significant advancement, demonstrating the potential for developing high-performance Zn-based batteries.



In Situ Construction of Multifunctional Phosphate Interphase Enabling Stable Zinc Anode with Fast Zn^{2+} Transport Kinetics

Junfeng Wang^{a,#}, Kaijian Yan^{b,#}, He Qi^{a,#}, Dongming Xu^a, Shaojie Guo^a, Lihua Pei^a, Zeya Peng^a, Dekang Huang^a, Yanzhu Luo^{a,*}, Feifei Cao^{a,*}

^a College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

^b State Key Laboratory of Advanced Technology for Materials Synthesis and Processing, School of Materials Science and Engineering, Wuhan University of Technology, Wuhan 430070, P. R. China
Email: luoyanzhu@mail.hzau.edu.cn; caofeifei@mail.hzau.edu.cn

[#]These authors contributed equally to this work.

Keywords: Interphase layer; $\text{Zn}(\text{PO}_3)_2$; Fast Zn^{2+} transport; Zinc anode; Zinc-ion battery

Abstract: Aqueous Zinc-ion batteries have significant potential application in large-scale energy storage due to their high safety, affordability, and high energy density. However, serious dendrite growth and side reactions, primarily caused by uneven zinc deposition and direct electrolyte contact, significantly reduce the lifespan of Zn metal anode. Here, we introduce a multifunctional zinc phosphate interphase on the ultrahigh-oriented Zn (002) texture. It is fabricated *in-situ* on Zn foil with no boundary through a straightforward one-step annealing method. The highly-conductive zinc phosphate interphase is thin with approximately 40 nm thickness. It facilitates rapid Zn-ion transport kinetics and promotes uniform zinc deposition through an epitaxial growth strategy. Additionally, the insulating and stable interphase inhibits corrosion and the hydrogen evolution reaction. As a result of these advantages, the modified Zn foils demonstrate excellent electrochemical performance. In



1 symmetrical cells, the zinc phosphate interphase modified Zn anode operates continuously for over
2 1400 h at an ultrahigh current density of 100 mA cm⁻² and has an outstanding cycle lifespan of 5900
3 h at 0.5 mA cm⁻². This sustainable protection strategy for the Zn anode lays the foundation to develop
4 high-performance electrodes for aqueous Zn-ion batteries.

5 1 Introduction

6 Rechargeable aqueous Zn-ion batteries (AZIBs) are extensively regarded as the most promising
7 solution for large-scale stationary energy storage systems due to their high theoretical gravimetric and
8 volumetric energy density (820 mA h g⁻¹ and 5855 mA h cm⁻³), low redox potential (-0.76 V vs. SHE),
9 high safety, and low cost (approximately ~US\$ 2.5 kg⁻¹).¹⁻³ However, two significant obstacles hinder
10 the further implementation of Zn anodes. The primary concern arises from the growth of Zn
11 protrusions/dendrites due to the uneven distribution of the electric field and Zn²⁺ flux, resulting in
12 inferior Columbic efficiency (CE) and a shortened lifespan of AZIBs.⁴⁻⁶ Moreover, the more negative
13 reduction potential of Zn²⁺/Zn (-0.76 V vs. SHE) compared with H₂O/H₂ (-0.41 V vs. SHE) in neutral
14 electrolytes leads to the corrosion of metallic Zn and the hydrogen evolution reaction (HER) on the
15 anode, ultimately reducing the reversibility and stability of active Zn. Thus, suppressing metal
16 dendrites and side reactions is crucial for the practical application of Zn metal anodes.⁷⁻¹⁰

17 To address the aforementioned issues, regulating the surface state of the Zn metal anode is
18 essential to achieve highly reversible Zn anodes.¹¹⁻¹³ Consequently, various strategies have been
19 proposed, such as designing 3D conductive hosts, alloying Zn, preferentially orienting along specific
20 crystal plane, and constructing interfacial protection layers, among others.¹⁴⁻¹⁶ The deposited Zn flakes
21 along the (002) plane have a slight angle of approximately 0°-30° with the substrate, which facilitates
22 uniform Zn metal deposition. Thus, constructing Zn electrodes with a higher exposure of this preferred



plane is regarded as an effective strategy to promote planar and dendrite-free Zn deposition. Additionally, owing to the higher free energy of H adsorption on the Zn (002) plane, it effectively inhibits side reactions.¹⁷⁻²⁰ For instance, an accumulative roll bonding methodology has been developed to fabricate Zn foil with a robust (002) texture, which is steadily increasing and ultimately reaching ~90% saturation after 12 cycles.²¹ However, most strategies are complicated and unable to realize the sole crystallographic orientation of Zn along the (002) plane, and there are still very few reports on the fabrication of single (002)-textured Zn.²² These findings indicate crucial need to control the crystal texture of Zn, minimizing other facets like (101), (100), and (102), while also simplifying and enhancing the effectiveness of the preparation procedure.

Additionally, the formation of a stable and robust interphase layer is critical to mitigating dendritic growth and improving interfacial stability of the Zn anode.²³⁻²⁵ Interphase layer on Zn anodes are typically classified as either in-situ formed, via electrolyte decomposition during cycling, or artificially constructed before cell assembly. In-situ interphase layer-such as those composed of ZnF_2 or ZnS -have been widely reported.²⁶⁻²⁷ The in-situ interphase layer is simple to form and naturally compatible with Zn. However, they often suffer from uncontrollable thickness, inhomogeneity, and poor mechanical durability under high current densities. In contrast, artificial interphase layer offers a more tunable and compositionally flexible strategy to design interfacial layers with well-defined structure, thickness, and functional properties. Among the reported artificial interphase layer, insoluble $\text{Zn}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$ has emerged as a highly promising candidate for interfacial protection layers in AZIBs in recent years.²⁸⁻²⁹ All of these studies demonstrate that $\text{Zn}_3(\text{PO}_4)_2$ exhibits lower desolvation activation energy and inhibits dendrites and corrosion. Nevertheless, the low ionic conductivity of $\text{Zn}_3(\text{PO}_4)_2$ ($7.2 \times 10^{-3} \text{ mS cm}^{-1}$) restricts the anode operation to low current densities ($<5 \text{ mA cm}^{-2}$). Unlike the isolated tetrahedral structure in $\text{Zn}_3(\text{PO}_4)_2$, $\text{Zn}(\text{PO}_3)_2$ features a substructure



1 formed by two bridging oxygen atoms between phosphorus-oxygen tetrahedra. The anionic network
2 forming the phosphate chain is able to offer sufficient sites for promoted Zn-ion adsorption, and the
3 created large void spaces could provide favorable channels or interstitial positions for cation diffusion
4 through the structure, thereby facilitating continuous cation transport.³⁰ Our previous work suggested
5 that the high zincphilic property of Zn surface could serve as ion pump to accelerate Zn^{2+} transport in
6 the electrolyte,³¹ and the thin interphase layer and good adhesion to the Zn substrate can also
7 significantly improve the batteries' electrochemical performance, especially the fast and continuous
8 ion transport behavior, as well as the durability of Zn.

9 Based on this motivation, we embarked on exploring a simple and economic approach to design
10 a highly-conductive $\text{Zn}(\text{PO}_3)_2$ protective interphase with a thin thickness and no interface with the Zn
11 substrate to promote both the cycling stability and the high rate capability of AZIBs. Here, we report
12 a straightforward one-step annealing method to fabricate $\text{Zn}(\text{PO}_3)_2$ interface to directly rooted on the
13 Zn substrate. As expected, a strongly oriented textured Zn with only (002) crystal plane is achieved
14 in this thermal treatment process due to the robust interaction between $\text{Zn}(\text{PO}_3)_2$ and the (002) crystal
15 plane. The solid electrolyte interphase layer exhibits no interface with the substrate, thereby delivering
16 remarkable properties for rapid Zn^{2+} transport and effectively promotes uniform and dendrite-free Zn
17 deposition behavior. Consequently, symmetric cells demonstrate extended cycling life exceeding
18 1400 h at an ultrahigh current density of 100 mA cm^{-2} and 5900 h at 0.5 mA cm^{-2} . These features
19 highlight the significant application potential of the $\text{Zn}(\text{PO}_3)_2$ interphase in AZIBs.

20 2 Results and discussion

21 A thin zinc phosphate interphase (referred to as P-Zn) is grown *in-situ* on commercial Zn foil
22 through a simple one-step annealing process using $\text{NaH}_2\text{PO}_4 \cdot 2\text{H}_2\text{O}$ as the phosphorus source,



1 facilitating scalability for practical applications (Fig. S1 and S2). During annealing at 390 °C under
2 Ar atmosphere, the decomposition of $\text{NaH}_2\text{PO}_4 \cdot 2\text{H}_2\text{O}$ released reactive phosphorus species that
3 reacted with the Zn surface to form a conformal zinc phosphate interphase layer. Simultaneously, the
4 high-temperature phosphorus-rich environment promoted surface energy-driven recrystallization and
5 atomic diffusion, leading to the preferential exposure of the Zn (002) crystal plane-known to possess
6 the lowest surface energy in the hexagonal close-packed Zn lattice. As illustrated in the AFM image
7 (Fig. S3), bare Zn exhibits noticeable scratches. They likely originate from the sanding procedure
8 during preparation, which can result in uneven Zn deposition. Following the *in-situ* phosphating
9 process, SEM images clearly show that the surface of the P-Zn foil is uniform (Fig. 1a), with the
10 original scratches obscured by numerous generated nanoparticles (Fig. 1b), promoting uniform Zn
11 nucleation and deposition behaviour. The significantly reduced contact angle also indicates an
12 alteration in the morphological and chemical characteristics of P-Zn because the newly generated
13 nanograins effectively regulate the contact behaviour between the electrolyte and P-Zn foil. The
14 outcome is greatly improved wettability of Zn anode and electrolyte (Fig. S4). X-ray diffraction (XRD)
15 analysis was further conducted to investigate the crystal structure and composition of the Zn electrodes
16 (Fig. 1c). Interestingly, compared with the original Zn foil, an exceptional crystallographic orientation
17 of Zn along (002) lattice plane has been exhibited in the XRD pattern of P-Zn, implying that atomic
18 rearrangement during annealing promotes texture formation. The absence of a detected interphase in
19 the XRD pattern may be attributed to its 40 nm-thin nature and nanoscale grain size.³² However,
20 without the assistance of phosphorus source, the Zn (002) orientation is not as strong as that of the P-
21 Zn (Fig. S5). These experimental results confirm the synergistic effect of thermal annealing and
22 phosphorus source in transforming Zn into a crystal facet with minimal surface energy, as the metal
23 atoms exhibit high mobility and migration capability under high temperature.³³

The composition of the formed interphase was also analyzed by X-ray photoelectron spectroscopy (XPS) coupled with Ar⁺ sputtering. In the P 2p spectra (Fig. 1d), P-Zn shows a signal at 133.5 eV, indicating the presence of P-O bonds. With ongoing Ar⁺ sputtering, the intensity of the P elements gradually diminishes, becoming minimal after 3 min and completely disappearing after 5 min. The peaks at 133.5 eV correspond with the presence of P⁵⁺, indicating that zinc phosphate is the dominant component on the surface.³⁴ Conversely, the signal of Zn 3s increases with sputtering depth, shifting from 140.2 eV to 139.3 eV after 3 min of sputtering. This finding indicates a reduction in valence from Zn²⁺ in zinc phosphate to metallic zinc, which is also confirmed by the Zn 2p spectra (Fig. S6).

Time-of-flight secondary-ion mass spectrometry (TOF-SIMS) was conducted to investigate the spatial distribution and chemical composition of the P-Zn layer. The interphase products including PO₃ and Zn species are observed on the surface of P-Zn. The content remains stable during the initial 180 s of sputtering, with the signal of PO₃ decreases rapidly while the spatial distribution of Zn increases (Fig. 1e), and the signal of PO₄ is negligible compared to the PO₃, suggesting the existence of the Zn(PO₃)₂ composite in the interphase layer. The 3D distribution of P and Zn elements confirms the close integration and absence of interface between the interphase and substrate (Fig. 1f-1h). The uniformity and thickness of the interphase layer is further investigated using high-angle annular dark-field scanning transmission electron microscope (HAADF-STEM) imaging through a standard focused-ion beam lift-out procedure (Fig. 1i and Fig. S7). Analysis of the sample's cross-sectional view clearly shows that the newly generated interphase is densely and uniformly distributed on the surface of Zn foil. It has an average thickness of 40 nm, the thinnest reported for artificial interphase layer in literature to our knowledge (Fig. S8). This thin layer effectively shortens ion-diffusion paths and facilitates the rapid transport of Zn²⁺. Additionally, the formed interphase penetrates the Zn



substrate without boundaries. The *in-situ* formed interphase significantly enhances contact with the Zn substrate, enhancing the stability of the Zn anode during cycling. Furthermore, elemental mappings indicate that the interphase layer comprises of O, P, and Zn, and the $\text{Zn}(\text{PO}_3)_2$ is located on the top of the metallic Zn (Fig. 1j). This finding is also confirmed by the line-scan elemental mappings because the signal of P and O elements in the surface region is definitely higher than that in the inner region (Fig. S9). The lattice fringes of 0.241 and 0.282 nm in the HRTEM images can also be well assigned to the (221) and (130) crystal planes of $\text{Zn}(\text{PO}_3)_2$ (Fig. 1k, 1l). The HRTEM image of the interphase powder scrapped from the surface of the P-Zn also manifest the existence of (-221) crystal planes of $\text{Zn}(\text{PO}_3)_2$ (Fig. S10), reconfirming the $\text{Zn}(\text{PO}_3)_2$ phase of the interphase layer. The strong orientation of P-Zn along the (002) plane is further confirmed by HRTEM (Fig. S11), which is consistent with the XRD result. Numerous clear parallel lattice fringes with 0.25 nm distance are evident in the region below the $\text{Zn}(\text{PO}_3)_2$ layer, which correspond to the Zn (002) plane.

Constructing an interfacial protection layer requires good electronic insulation and ionic conductivity, which are essential for developing dendrite-free and high-performance zinc anodes. Four-point resistance measurements were conducted to assess resistivity, revealing that the resistivity of the P-Zn anode is $6.52 \mu\Omega\cdot\text{cm}$, higher than that of bare Zn ($5.63 \mu\Omega\cdot\text{cm}$; Fig. S12). The $\text{Zn}(\text{PO}_3)_2$ interphase, characterized by good electronic insulation, facilitates Zn deposition beneath the passivation layer, preventing direct contact with the electrolyte and thereby inhibiting side reactions. Ionic conductivity, as a crucial aspect of the interphase, is also essential for achieving high-performance zinc anodes. The ionic conductivities of the $\text{Zn}(\text{PO}_3)_2$ interphase were determined by impedance spectroscopy, revealing a high conductivity of 32.3 mS cm^{-1} . This value is an improvement of several orders of magnitude compared with other reported interphase layers, especially $\text{Zn}_3(\text{PO}_4)_2$ interphase (Fig. 2a).^{29-30, 34-36}



1 To assess the impact of the $\text{Zn}(\text{PO}_3)_2$ interphase on Zn plating/stripping behavior, we assembled
2 and tested $\text{Zn}||\text{Cu}$ half-cells using bare Zn and P-Zn foils as working electrodes, which were tested at
3 a current density of 10.0 mA cm^{-2} . The CE of $\text{Zn}||\text{Cu}$ half-cells based on the bare Zn foils suddenly
4 decrease due to Zn dendrite growth after 160 cycles. Using P-Zn foils as working electrodes, the cells
5 quickly increase the CE to 99.7% and remain stable over 1500 cycles (Fig. 2b). The nucleation
6 overpotential of the P-Zn||Cu half-cell is 156 mV, whereas that of bare Zn||Cu is 132 mV (Fig. S13).
7 A higher nucleation overpotential results in finer-grained Zn deposition with a favorable
8 crystallographic orientation, thereby inhibiting dendrite growth. Electrochemical impedance
9 spectroscopy of the symmetric cells was conducted to compare the electrochemical performance
10 differences between bare Zn and P-Zn anodes. Given the insulating properties of the metaphosphate
11 interphase, the impedance of the P-Zn symmetrical cell before cycling is slightly higher than that of
12 bare Zn (Fig. S14). After 100 cycles at 1 mA cm^{-2} and 1 mA h cm^{-2} , the impedance of the P-Zn
13 symmetric cell is lower than that of the bare Zn symmetric cell (Fig. 2c). Rapid charge-transfer
14 kinetics are beneficial for the swift transport of Zn^{2+} ions and the long-term stability of the electrode.
15 Fig. 2d illustrates the rate performance of symmetric cells at current densities ranging within 1-100
16 mA cm^{-2} , maintaining a fixed capacity of 1.0 mA h cm^{-2} . Bare Zn symmetric cells experience severe
17 short circuits at 100 mA cm^{-2} during testing. Conversely, P-Zn symmetric cells demonstrate
18 significantly less voltage hysteresis and maintain stable voltage profiles, even at an ultrahigh current
19 density of 100 mA cm^{-2} . Moreover, they continue to operate as the current density returns to 1 mA
20 cm^{-2} . Depth of discharge is also crucial to the practical application of Zn anodes. Despite a harsh
21 condition with the 88.1% depth of discharge ($20 \mu\text{m}$ Zn foil), the P-Zn electrode maintained stable
22 cycles for 320 h (Fig. 2e). The ion-transport rate is a limiting factor for electrodeposition under high-
23 rate conditions. Remarkably, P-Zn symmetric cells exhibit stable cycling over 1400 h (approximately




16000 cycles) at an ultra-high current density of 100 mA cm^{-2} , demonstrating excellent rate performance (Fig. 2f). The P-Zn symmetric cells achieve an ultrahigh cumulative capacity of over 16 A h cm^{-2} , surpassing that of most materials reported in literature (Fig. 2g).^{5, 37-43} Accelerated Zn^{2+} migration and homogenized interfacial Zn^{2+} distribution also contribute to a significantly prolonged cyclic life ($>5900 \text{ h}$) in P-Zn symmetric cells at 0.5 mA cm^{-2} and 0.5 mA h cm^{-2} , nearly seven times longer than that of bare Zn cells (Fig. 2h). The stable $\text{Zn}(\text{PO}_3)_2$ interphase layer also effectively prevents continuous electrolyte consumption and inhibits zinc dendrite growth during cycling, resulting in excellent cycling stability at various current densities (Fig. S15).

Deposition behavior is the key factor affecting the electrochemical performance of the Zn anode. To illustrate the regulatory effect of the P-Zn layer, SEM was used to investigate the morphological evolution of Zn anodes with deposition capacities of 1, 5, and 10 mA h cm^{-2} . The poor wettability and zincophilicity of bare Zn lead to uneven Zn^{2+} flux over the electrode surface, resulting in the formation of scattered spot-shaped deposits (Fig. 3a). As the deposition capacity increases, the electrode surface becomes covered by porous and loose Zn, along with byproducts (Fig. 3b). Eventually, dense upright hexagonal Zn flakes form on the bare Zn anode, posing a risk of short circuits (Fig. 3c). Therefore, the P-Zn electrode exhibits a flat and compact surface after various deposition capacities (Fig. 3d-f). The high diffraction intensity of the (101) plane of the bare Zn anode indicates that Zn^{2+} tends to deposit in the vertical direction. Conversely, the Zn (002) plane of P-Zn consistently dominates among all planes, and even under a deposition of 10 mA h cm^{-2} , the ratio of intensity of the (002) plane to the (101) plane is 38.2 (Fig. 3g). The (002) crystal face of Zn has minimal surface energy, promoting parallel Zn growth on the electrode plane rather than vertical growth, thereby significantly inhibiting dendrite formation. Additionally, *in-situ* optical microscopy was conducted to monitor Zn deposition behavior. After 15 min, numerous protrusions appear on bare Zn, evolving into a mossy and rough



1 surface (Fig. 3h). The tip effect increases charge density on prominent areas, exacerbating Zn dendrite
2 formation and reducing the cycling life of AZIBs. By contrast, P-Zn electrode exhibits relatively
3 homogeneous deposition without visible dendrites throughout the process (Fig. 3i). To better
4 understand Zn plating/stripping features during cycling, the morphology of bare Zn and P-Zn
5 electrodes was investigated after varying numbers of cycles. Results show that the P-Zn surface
6 remains smooth even after 100 cycles (Fig. S16). Thus, the P-Zn layer effectively guides and stabilizes
7 uniform Zn deposition, which is essential for achieving ultrahigh cycling stability. We also
8 investigated the stability of the P-Zn interface layer after cycling. Symmetric P-Zn||P-Zn cells were
9 disassembled after 5 cycles at a current density of 5 mA cm⁻² for HAADF-STEM imaging and
10 corresponding elemental mapping analysis, as well as the HRTEM and TOF-SIMS analyses. As
11 shown in Fig. S17, the P-Zn interfacial layer maintains its structural integrity after cycling.
12 Furthermore, the elemental mapping results confirm that Zn is uniformly deposited beneath the P-Zn
13 interfacial layer, without inducing structural collapse or disruption of the protective layer. The
14 HRTEM results of the interphase powder scrapped from the surface of the cycled P-Zn reveal well-
15 preserved lattice fringes of 0.281 and 0.298 nm, corresponding to the (130) and (-221) planes of
16 Zn(PO₃)₂ (Fig. S18), confirming the preservation of the metaphosphate structure. Meanwhile, TOF-
17 SIMS depth profiling shows dominant PO₃⁻ signals with negligible PO₄³⁻ species throughout
18 sputtering (Fig. S19), indicating minimal hydrolysis or transition into orthophosphate phases. These
19 observations suggest that the P-Zn layer effectively regulates Zn deposition and preserves interfacial
20 stability during repeated plating/stripping cycles. Meanwhile, the diffraction peaks of
21 Zn₄SO₄(OH)₆·5H₂O (ZHS) of cycled bare Zn can be clearly observed, indicating the occurrence of
22 irreversible side reactions, which is absent in the cycled P-Zn samples (Fig. S20). As shown in Fig.
23 3j, the surface height difference of cycled bare zinc reaches 20 μm with visible pits, whereas P-Zn



electrode surface maintains a smooth surface (Fig. 3k). Furthermore, cross-section SEM images show significant differences in Zn deposition behavior between bare Zn and P-Zn anodes, given the denser and smoother morphology of deposited Zn in the P-Zn anode than in bare Zn anode after cycling (Fig. 3l, 3m).

To further comprehend Zn diffusion behavior during deposition, chronoamperometry tests were conducted (Fig. S21). The lower current observed with P-Zn indicates reduced 2D diffusion process because lateral Zn^{2+} diffusion is hindered, preventing dendrite growth. This phenomenon is attributed to the homogeneous nanoparticles in the $\text{Zn}(\text{PO}_3)_2$ interphase and its zincophilic property. Tafel curve tests were performed to evaluate the corrosion resistance of the anodes. The presence of the $\text{Zn}(\text{PO}_3)_2$ interphase layer reduces the corrosion current from 0.59 mA cm^{-2} for bare Zn to 0.036 mA cm^{-2} for P-Zn (Fig. S22), indicating suppressed corrosion. This finding is attributed to the effective isolation of Zn from direct contact with the electrolyte by the $\text{Zn}(\text{PO}_3)_2$ layer. The effect of the P-Zn layer on inhibiting the hydrogen evolution reaction also analyzed using a three-electrode system. The current density of P-Zn electrode is always lower than that of bare Zn over the entire potential range (Fig. S23). Furthermore, symmetric cells were assembled and left to stand for 20 days to intuitively illustrate the effect of P-Zn layer in inhibiting parasitic reactions. Remarkably, the thickness of the symmetric cell with bare Zn electrode increases from 3.23 mm to 3.81 mm, whereas the thickness of the P-Zn symmetric cell shows minimal change from 3.23 mm to 3.25 mm (Fig. S24). This finding indicates significantly reduced corrosion and hydrogen evolution reactions.

DFT calculations were performed to determine the reason for the strong orientation of P-Zn along the (002) plane following the phosphating process. These calculations assess the interactions between the (002), (100), and (101) Zn planes with the $\text{Zn}(\text{PO}_3)_2$ interphase layer (Fig. 4a). The adsorption energies of the Zn (002), (101), and (100) crystal planes with the $\text{Zn}(\text{PO}_3)_2$ layer are -50.7, -43.8, and



-3.9 eV, respectively (Fig. 4b). The significant interaction with the Zn (002) crystal plane promotes the preferred orientation of the (002) crystal plane due to the synergistic effect of thermal radiation. Efficient Zn^{2+} transport within the interphase layer is crucial for the electrode's rate performance. An in-depth study of migration path and energy barrier of Zn^{2+} in the $\text{Zn}(\text{PO}_3)_2$ interphase layer was conducted to explore the cause of the outstanding electrochemical performance of the anode at high current density (Fig. S25). Specifically, Zn^{2+} preferentially migrates along the c-axis of the $\text{Zn}(\text{PO}_3)_2$ crystal, encountering a minimum migration barrier of only 0.99 eV (Fig. 4c-d and Fig. S26-27), surpassing other fast Zn-ion conductors reported in literature.⁴⁴⁻⁴⁵ This highly efficient Zn^{2+} diffusion behavior ensures excellent high-rate performance and reversibility, leading to a dendrite-free Zn anode.

Based on the experimental findings above, a schematic summarizing the Zn deposition and stripping behavior on bare Zn and P-Zn electrodes is presented in Fig. 4e. Direct contact of Zn with the aqueous electrolyte on bare Zn leads to severe side reactions and irregular Zn deposition, ultimately resulting in dendritic growth. Conversely, the insulating nature of the $\text{Zn}(\text{PO}_3)_2$ interphase layer promotes Zn^{2+} deposition beneath it, thereby suppressing the corrosion and passivation of the Zn anode. The strong binding force between the P-Zn layer and the substrate accommodates the dynamic volume changes of the Zn anode during cycles, preventing continuous electrolyte consumption. Fast zinc-ion transport, a low migration barrier, and short diffusion paths enable rapid zinc plating and stripping at high current densities on the Zn anode. The high orientation along the Zn (002) crystal plane facilitates ordered Zn epitaxial deposition, resulting in dense and dendrite-free Zn growth.

The effectiveness of the $\text{Zn}(\text{PO}_3)_2$ interphase layer in suppressing Zn dendrite formation and side reactions is demonstrated by the significantly enhanced long-term cycling stability of symmetric cells



1 and the uniform Zn deposition. Additionally, aqueous $\text{Zn}||\text{NH}_4\text{V}_4\text{O}_{10}$ (NVO) and
2 $\text{Zn}||\text{K}_{0.27}\text{MnO}_2 \cdot 0.54\text{H}_2\text{O}$ (KMO) full cells were assembled to comprehensively assess the practical
3 applicability of the P-Zn anode in various cathode systems. The NVO nanorods were synthesized via
4 a hydrothermal method and confirmed by XRD and SEM (Fig. S28). As illustrated in Fig. 5a, both
5 Bare Zn and P-Zn based full cells show similar redox peaks in their CV profiles, indicating that the
6 interfacial layer modification does not alter the fundamental electrochemical redox mechanism of the
7 cathode material. However, the P-Zn||NVO cells exhibit superior rate capability and consistently
8 higher specific capacities across a wide current density range ($1.0\text{--}5.0\text{ A g}^{-1}$), as shown in Fig. 5b. This
9 performance enhancement indicates improved reaction kinetics and suppressed side reactions, as
10 further supported by the reduced interfacial resistance observed in the EIS spectra at all states of
11 charge (SOC) of 20%, 50%, and 70% (Fig. S29). Realistic aqueous zinc-ion batteries must consider
12 key practical parameters such as the N/P ratio, active mass loading, and E/C ratio.⁴⁶ To validate the
13 real-world applicability of the P-Zn design, full cells were further constructed under stringent practical
14 conditions, including a thin zinc foil ($20\text{ }\mu\text{m}$), a high-mass-loading NVO cathode (12.5 mg cm^{-2}), a
15 low N/P ratio of 1.8, and a low E/C ratio of $14.7\text{ }\mu\text{L mAh}^{-1}$. Under these conditions, the P-Zn||NVO
16 cell maintained stable cycling performance for 320 cycles with a high specific capacity of 161 mA h
17 g^{-1} (Fig. 5c). Long-term cycling results further verify the stability of the interfacial design: at a current
18 density of 2 A g^{-1} with an N/P ratio of 3.8, the cell delivered a specific capacity of 276 mA h g^{-1} and
19 retained excellent capacity over 800 cycles (Fig. S30). Under high-rate conditions of 5 A g^{-1} , the P-
20 Zn||NVO cell achieved a stable discharge capacity of 257 mA h g^{-1} over 1000 cycles (Fig. S31).
21 Although AZIBs often suffer from poor cycling stability at low current densities due to intensified
22 side reactions, the P-Zn||NVO cell still delivers significantly improved cycling performance compared
23 to the Zn||NVO cell even at a low current density of 30 mA g^{-1} (Fig. S32), underscoring the durability

1 of the engineered interphase. In addition, $K_{0.27}MnO_2 \cdot 0.54H_2O$ cathode materials were synthesized via
2 a facile sol-gel method, incorporating K^+ ions into MnO_2 nanoparticles to enhance structural stability
3 and ion diffusion kinetics (Fig. S33). Pre-intercalated K^+ ions suppress Mn dissolution and help
4 maintain structural integrity, making it an excellent zinc storage material. As shown in the SEM image,
5 the diameter of KMO particles is approximately 100 nm. Bare Zn||KMO and P-Zn||KMO AZIBs
6 exhibit similar redox peaks in the CV curves (Fig. 5d), and the improved reaction kinetics reduces the
7 overpotential of the P-Zn||KMO full cell. Additionally, the larger integrated area under the CV curve
8 suggests higher electrochemical activity for the P-Zn||KMO full cell, which is further supported by
9 the lower interfacial resistance observed at all SOC levels of 20%, 50%, and 70% (Fig. S34). As
10 shown in Fig. 5e, the P-Zn||KMO full cell performs better at different current densities. The specific
11 capacity of the bare Zn||KMO full cell significantly decreases to 92 mA h g^{-1} with a capacity retention
12 of 47% after 800 cycles at 1 A g^{-1} . Meanwhile, the P-Zn||KMO full cell exhibits significantly improved
13 cycling performance even at a low current density of 30 mA g^{-1} (Fig. S35). Conversely, a high
14 reversible capacity of 170 mA h g^{-1} can be obtained for P-Zn||KMO-based AZIBs after 800 cycles
15 (Fig. 5f and Fig. S36). Pouch cells were assembled to further assess the practicality of the P-Zn anode.
16 A $6 \text{ cm} \times 6 \text{ cm}$ single-layer pouch cell was tested, and results are shown in Fig. 5g. It has a specific
17 capacity of 145 mA h g^{-1} , retaining approximately 72% of its capacity after 200 cycles at 1 A g^{-1} .
18 Additionally, laminated pouch cells are successfully assembled alongside the single-layer
19 configuration. Fig. 5h illustrates the practical application of the laminated pouch cell. Series
20 connection of two single cells, the pouch cell attains a voltage of 3 V. The laminated pouch cell can
21 also reliably illuminate the light-emitting diode indicator of HZAU. The above findings demonstrate
22 that P-Zn anodes hold the potential for wide-ranging applications due to their excellent
23 electrochemical properties.



3 Conclusion

We present an *in-situ* 40 nm-thin highly-conductive $\text{Zn}(\text{PO}_3)_2$ interphase layer with excellent zinc-ion transport properties, effectively combining zincophilic, hydrophilic, and insulative properties to produce a dendrite-free Zn anode. Due to its *in-situ* growth strategy and anionic substructure of phosphate chains, the P-Zn anode, featuring a thin $\text{Zn}(\text{PO}_3)_2$ interphase layer with a thickness of only 40 nm, demonstrates excellent stability and remarkable rate performance during cycling. Through visualization methods and theoretical calculations, the rooted homogeneous $\text{Zn}(\text{PO}_3)_2$ layer is confirmed to enhance the migration of Zn^{2+} ions and optimize the Zn deposition, effectively mitigating Zn dendrite formation. Consequently, symmetrical cells with P-Zn anodes exhibit remarkable cycling performance at an ultrahigh current density of 100 mA cm^{-2} , enduring over 16000 cycles. Furthermore, they also demonstrate an exceptional cycle lifespan of 5900 h at 0.5 mA cm^{-2} and 0.5 mA h cm^{-2} . When assembled in full cells with NVO or KMO cathodes, the P-Zn anode delivers excellent electrochemical performance. The P-Zn||NVO cell achieves a high specific capacity of 276 mA h g^{-1} with 92.6% capacity retention over 800 cycles at 2 A g^{-1} . Even at a low N/P ratio of 1.8, the full cell maintains a high capacity of 161 mA h g^{-1} over 320 cycles. The P-Zn||KMO configuration also exhibits long-term cycling stability, retaining a capacity of 170 mA h g^{-1} over 800 cycles at 1 A g^{-1} . Additionally, the assembled pouch cell demonstrates promising durability, supporting the scalability of the approach. The comprehensive performance of the P-Zn anode is at an advanced level, showing high potential for the development of advanced Zn-based batteries with superior electrochemical performance.

Author information

Corresponding Author



Feifei Cao- College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China;

Email: caofeifei@mail.hzau.edu.cn

Yanzhu Luo- College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China;

Email: luoyanzhu@mail.hzau.edu.cn

Authors

Junfeng Wang-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Kaijian Yan-State Key Laboratory of Advanced Technology for Materials Synthesis and Processing, International School of Materials Science and Engineering, Wuhan University of Technology, Wuhan, 430070, P. R. China

He Qi-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

DongMing Xu-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Shaojie Guo-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Lihua Pei-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Zeya Peng-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Dekang Huang-College of Chemistry, Huazhong Agricultural University, Wuhan 430070, P. R. China

Notes

The authors declare no competing financial interest.

Acknowledgements

The research was financially supported by the National Natural Science Foundation Regional Innovation and Development Joint Fund (U23A20684), National Natural Science Foundation of China (52272208, 52572226), and the Fundamental Research Funds for the Central Universities of China (2662025HXPY005, 2662025HXPY004). The authors gratefully acknowledge Prof. Congli Sun (Wuhan University of Technology) and Jiajing Wang (Wuhan University of Technology) for their assistance in obtaining high-quality HAADF-STEM image and EDS results that significantly supported the structural analysis in this work.

Author Contributions

F. C. and Y. L. supervised the research. J. W., Y. L., and D. H. conceived the project, analyzed the data, and wrote the manuscript. J. W., H. Q., K. Y., S. G., L. P., and P. Z. conducted experiments and collected data. D. X. gave helpful advice on manuscript preparation.



Reference

- (1) S. Gourley, R. Brown, B. Adams, D. Higgins, *Joule* 2023, **7**, 1415-1436.
- (2) Y. Liu, X. Lu, F. Lai, T. Liu, P. Shearing, I. Parkin, G. He, D. Brett, *Joule* 2021, **5**, 2845-2903.
- (3) Z. Zhu, T. Jiang, M. Ali, Y. Meng, Y. Jin, Y. Cui, W. Chen, *Chem. Rev.* 2022, **122**, 16610-16715.
- (4) F. Li, D. Ma, K. Ouyang, M. Yang, J. Qiu, J. Feng, Y. Wang, H. Mi, S. Sun, L. Sun, C. He, P. Zhang, *Adv. Energy Mater.* 2023, **13**, 2204365.
- (5) L. Ma, Q. Li, Y. Ying, F. Ma, S. Chen, Y. Li, H. Huang, C. Zhi, *Adv. Mater.* 2021, **33**, e2007406.
- (6) F. Yang, J. Yuwono, J. Hao, J. Long, L. Yuan, Y. Wang, S. Liu, Y. Fan, S. Zhao, K. Davey, Z. Guo, *Adv. Mater.* 2022, **34**, e2206754.
- (7) H. Jia, Z. Q. Wang, B. Tawiah, Y. D. Wang, C. Y. Chan, B. Fei, F. Pan, *Nano Energy* 2020, **70**, 104523.
- (8) W. Lu, C. Zhang, H. Zhang, X. Li, *ACS Energy Lett.* 2022, **6**, 2765.
- (9) B. Luo, Y. Wang, S. Zheng, L. Sun, G. Duan, J. Lu, J. Huang, Z. Ye, *Energy Storage Mater.* 2022, **51**, 610-619.
- (10) C. Nie, G. Wang, D. Wang, M. Wang, X. Gao, Z. Bai, N. Wang, J. Yang, Z. Xing, S. Dou, *Adv. Energy Mater.* 2023, **13**, 2300606.
- (11) F. Ling, L. Wang, F. Liu, M. Ma, S. Zhang, X. Rui, Y. Shao, Y. Yang, S. He, H. Pan, X. Wu, Y. Yao, Y. Yu, *Adv. Mater.* 2023, **35**, e2208764.
- (12) J. Yang, S. Wang, L. Du, S. Bi, J. Zhu, L. Liu, Z. Niu, *Adv. Funct. Mater.* 2024, **34**, 2314426.
- (13) N. Zhang, X. Chen, M. Yu, Z. Niu, F. Cheng, J. Chen, *Chem. Soc. Rev.* 2020, **49**, 4203-4219.
- (14) X. Geng, X. Hou, X. He, H. Fan, *Adv. Energy Mater.* 2024, **14**, 2304094.
- (15) H. Tian, J. Yang, Y. Deng, W. Tang, R. Liu, C. Xu, P. Han, H. Fan, *Adv. Energy Mater.* 2022, **13**, 2202603.
- (16) F. Xie, H. Li, X. Wang, X. Zhi, D. Chao, K. Davey, S. Qiao, *Adv. Energy Mater.* 2021, **11**, 2003419.
- (17) H. Cai, S. Bi, R. Wang, L. Liu, Z. Niu, *Angew. Chem. Int. Ed.* 2021, **61**, e202205472.
- (18) Z. Chen, T. Wang, Y. Hou, Y. Wang, Z. Huang, H. Cui, J. Fan, Z. Pei, C. Zhi, *Adv. Mater.* 2022, **34**, e2207682.
- (19) Q. Li, H. Hong, J. Zhu, Z. Wu, C. Li, D. Wang, P. Li, Y. Zhao, Y. Hou, G. Liang, F. Mo, H. Cui, C. Zhi, *ACS Nano* 2023, **17**, 23805-23813.



- (20) Y. Su, B. Chen, Y. Sun, Z. Xue, Y. Zou, D. Yang, L. Sun, X. Yang, C. Li, Y. Yang, X. Song, W. Guo, S. Dou, D. Chao, Z. Liu, J. Sun, *Adv. Mater.* 2023, **35**, e2301410.
- (21) J. Zheng, Y. Deng, J. Yin, T. Tang, R. Garcia-Mendez, Q. Zhao, L. Archer. *Adv. Mater.* 2022, **34**, e2106867.
- (22) Z. Chen, Q. Wu, X. Han, C. Wang, J. Chen, T. Hu, Q. He, X. Zhu, D. Yuan, J. Chen, Y. Zhang, L. Yang, Y. Ma, J. Zhao, *Angew. Chem. Int. Ed.* 2024, **63**, e202401507.
- (23) X. He, Y. Cui, Y. Qian, Y. Wu, H. Ling, H. Zhang, X. Kong, Y. Zhao, M. Xue, L. Jiang, L. Wen, *J. Am. Chem. Soc.* 2022, **144**, 11168-11177.
- (24) S. Pu, C. Gong, Y. Tang, Z. Ning, J. Liu, S. Zhang, Y. Yuan, D. Melvin, S. Yang, L. Pi, J. Marie, B. Hu, M. Jenkins, Z. Li, B. Liu, S. Tsang, T. Marrow, R. Reed, X. Gao, P. Bruce, A. Robertson, *Adv. Mater.* 2022, **34**, e2202552.
- (25) W. Wang, G. Huang, Y. Wang, Z. Cao, L. Cavallo, M. Hedhili, H. Alshareef, *Adv. Energy Mater.* 2022, **12**, 2102797
- (26) L. Cao, D. Li, T. Pollard, *Nat. Nanotechnol.* 2021, **16**, 902-910.
- (27) S. S. Shinde, J. Y. Jung, N. K. Wagh, *Nat. Energy.* 2021, **6**, 592-604.
- (28) J. Li, Z. Zheng, Z. Yu, F. She, L. Lai, J. Prabowo, W. Lv, L. Wei, Y. Chen, *J. Mater. Chem. A.* 2023, **11**, 3051-3059.
- (29) S. Zhang, M. Ye, Y. Zhang, Y. Tang, X. Liu, C. Li, *Adv. Funct. Mater.* 2023, **33**, 2208230.
- (30) G. Han, A. Vasylenko, A. Neale, B. Duff, R. Chen, M. Dyer, Y. Dang, L. Daniels, M. Zanella, C. Robertson, L. Kershaw Cook, A. Hansen, M. Knapp, L. Hardwick, F. Blanc, J. Claridge, M. Rosseinsky, *J. Am. Chem. Soc.* 2021, **143**, 18216-18232.
- (31) Z. Zheng, S. Guo, M. Yan, Y. Luo, F. Cao, *Adv. Mater.* 2023, **35**, 2304667.
- (32) C. F. Holder, R. E. Schaak, *Nanoscale Materials.* 2019, **13**, 7359.
- (33) H. Xie, M. Hong, E. M. Hitz, X. Wang, M. Cui, D. J. Kline, M. R. Zachariah, L. Hu, *J. Am. Chem. Soc.* 2020, **142**, 17364-17371.
- (34) S. Zhao, Y. Zhang, J. Li, L. Qi, Y. Tang, J. Zhu, J. Zhi and F. Huang. *Adv. Mater.* 2023, **35**, e2300195.
- (35) C. Cui, D. Han, H. Lu, Z. Li, K. Zhang, B. Zhang, X. Guo, R. Sun, X. Ye, J. Gao, Y. Liu, Y. Guo, R. Meng, C. Wei, L. Yin, F. Kang, Z. Weng, Q. Yang, *Adv. Energy Mater.* 2023, **13**, 2301466.
- (36) M. Liu, W. Yuan, G. Ma, K. Qiu, X. Nie, Y. Liu, S. Shen, N. Zhang, *Angew. Chem. Int. Ed.* 2023, **62**, e202304444. *Angew. Chem. Int. Ed.* 2023, **62**, e202304444.



- (37) Q. Cao, Y. Gao, J. Pu, X. Zhao, Y. Wang, J. Chen, C. Guan, *Nat. Commun.* 2023, **14**, 641.
- (38) Q. Hu, J. Hou, Y. Liu, L. Li, Q. Ran, J. Mao, X. Liu, J. Zhao, H. Pang, *Adv. Mater.* 2023, **35**, e2303336.
- (39) Z. Hu, F. Zhang, Y. Zhao, H. Wang, Y. Huang, F. Wu, R. Chen, L. Li, *Adv. Mater.* 2022, **34**, e2203104.
- (40) X. Luan, L. Qi, Z. Zheng, Y. Gao, Y. Xue, Y. Li, *Angew. Chem. Int. Ed.* 2023, **62**, e202215968.
- (41) P. Zhang, Z. Wu, S. Zhang, L. Liu, Y. Tian, Y. Dou, Z. Lin, S. Zhang, *Nano Energy* 2022, **102**, 107721.
- (42) Y. Qin, H. Li, C. Han, F. Mo, X. Wang, *Adv. Mater.* 2022, **34**, e2207118.
- (43) K. Zhu, C. Guo, W. Gong, Q. Xiao, Y. Yao, K. Davey, Q. Wang, J. Mao, P. Xue, Z. Guo, *Energy Environ. Sci.* 2023, **16**, 3612-3622.
- (44) X. Zeng, J. Mao, J. Hao, J. Liu, S. Liu, Z. Wang, Y. Wang, S. Zhang, T. Zheng, J. Liu, P. Rao, Z. Guo, *Adv. Mater.* 2021, **33**, 2007416.
- (45) L. Hong, X. Wu, Y. Liu, C. Yu, Y. Liu, K. Sun, C. Shen, W. Huang, Y. Zhou, J. Chen, K. Wang, *Adv. Funct. Mater.* 2023, **33**, 2300952.
- (46) S. S. Shinde, N. K. Wagh, C. H. Lee, D. H. Kim, S. H. U. Lee, J. H. Lee, *Adv. Mater.* 2023, **35**, 2303509.



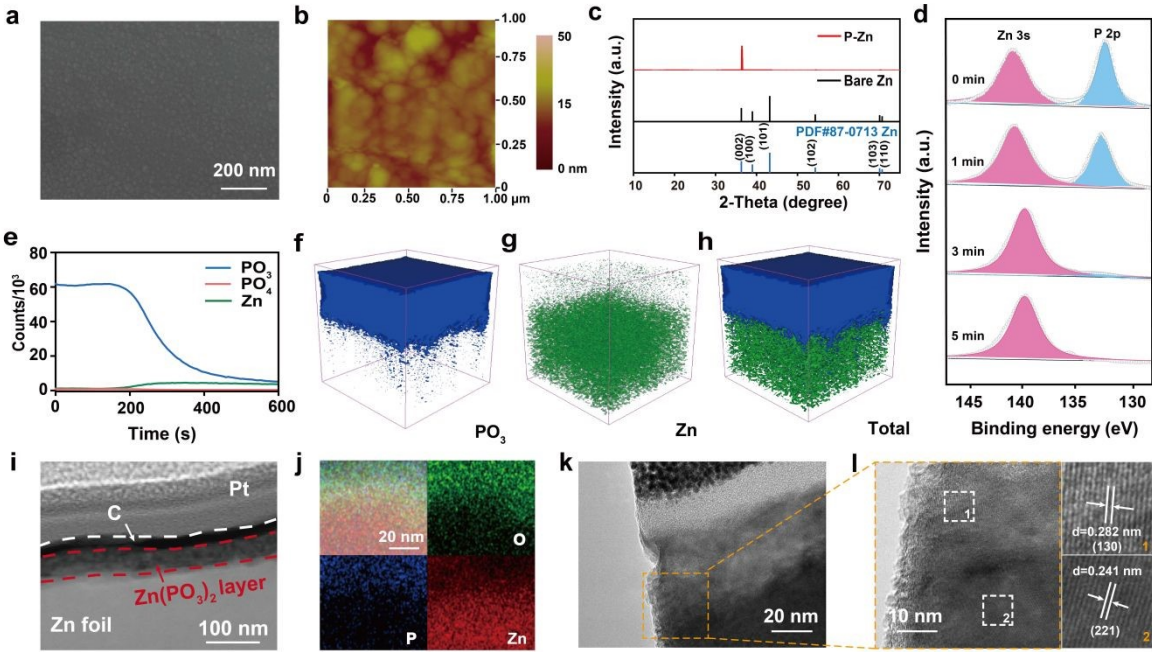


Fig. 1 (a) Top-view SEM images of P-Zn foil. (b) AFM images of P-Zn surface. (c) XRD patterns of P-Zn foil. (d) XPS depth analysis of P 2p and Zn 3s in P-Zn foil. (e-h) Profiles and spatial distribution of P and Zn elements on P-Zn foil detected by TOF-SIMS. (i) HAADF-STEM image of P-Zn interphase and (j) the corresponding elemental mappings. (k-l) HRTEM images of selected area of P-Zn foil.



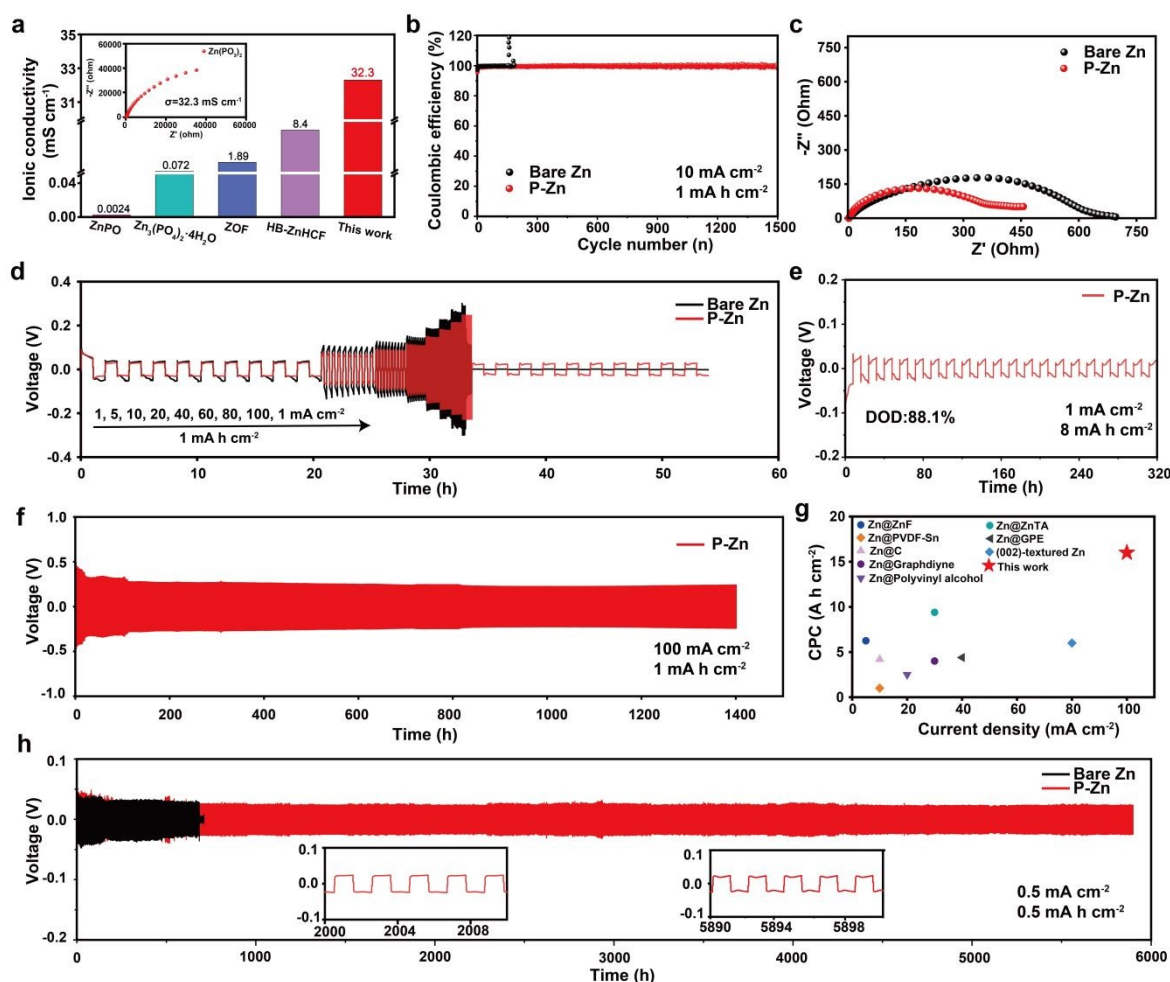


Fig. 2 (a) Comparison of interphase with previous reports in ionic conductivity, inset is the ion conductivity of Zn(PO₃)₂ interphase. (b) Coulombic efficiency of bare Zn||Cu and P-Zn||Cu cells. (c) Electrochemical impedance spectra of symmetric cells after 100 cycles. (d) Rate performances of bare Zn and P-Zn symmetric cells at various current densities. Cycling performance of the symmetric cells using bare Zn and P-Zn at (e) 1 mA cm⁻² and 8 mA h cm⁻², (f) 100 mA cm⁻² and 1 mA h cm⁻², and (h) 0.5 mA cm⁻² and 0.5 mA h cm⁻². (g) Comparison of the symmetrical cells with previous reports in current density and cumulative capacity.

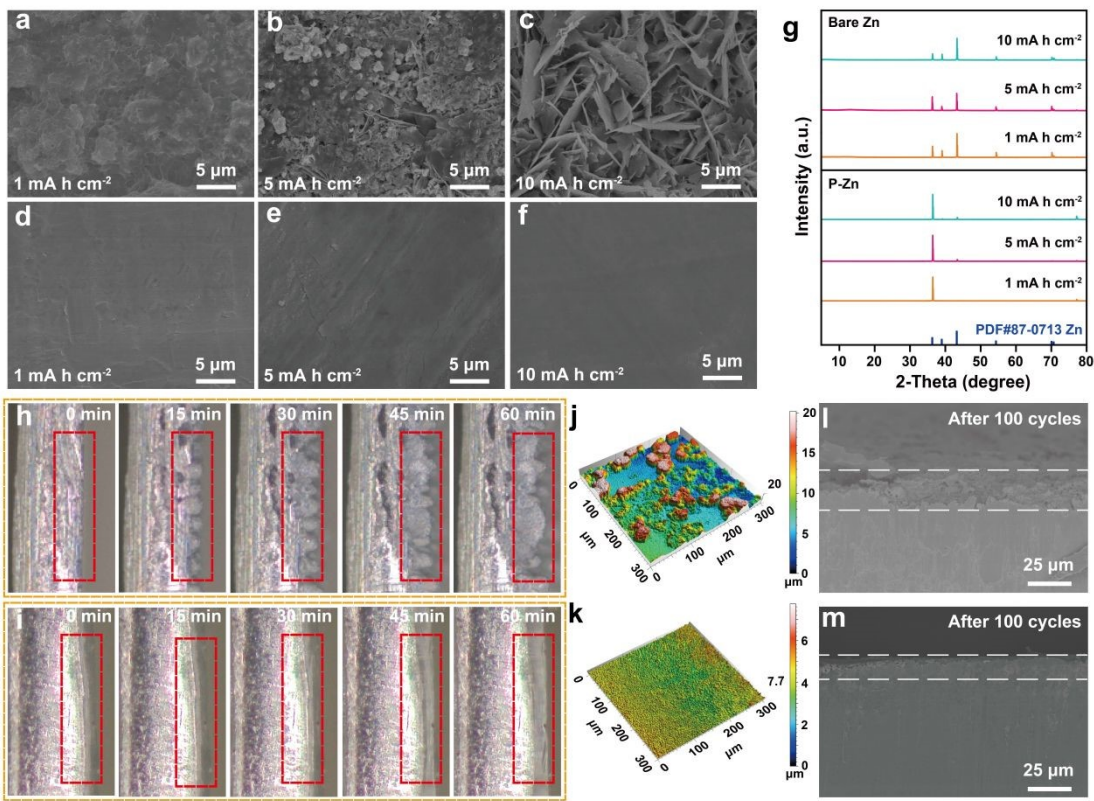


Fig. 3 Top-view SEM images of (a-c) bare Zn and (d-f) P-Zn electrodes after plating for 1, 5, and 10 mA h cm⁻² at 1 mA cm⁻². (g) XRD patterns of bare Zn and P-Zn electrodes after plating for 1, 5, and 10 mA h cm⁻² at 1 mA cm⁻². *In-situ* optical microscope observations of zinc deposition on (h) bare Zn and (i) P-Zn foil. Confocal laser scanning microscope images of (j) bare Zn and (k) P-Zn electrodes after 100 cycles. Cross-section SEM images of (l) bare Zn and (m) P-Zn electrodes after 100 cycles at 1 mA cm⁻² and 1 mA h cm⁻².

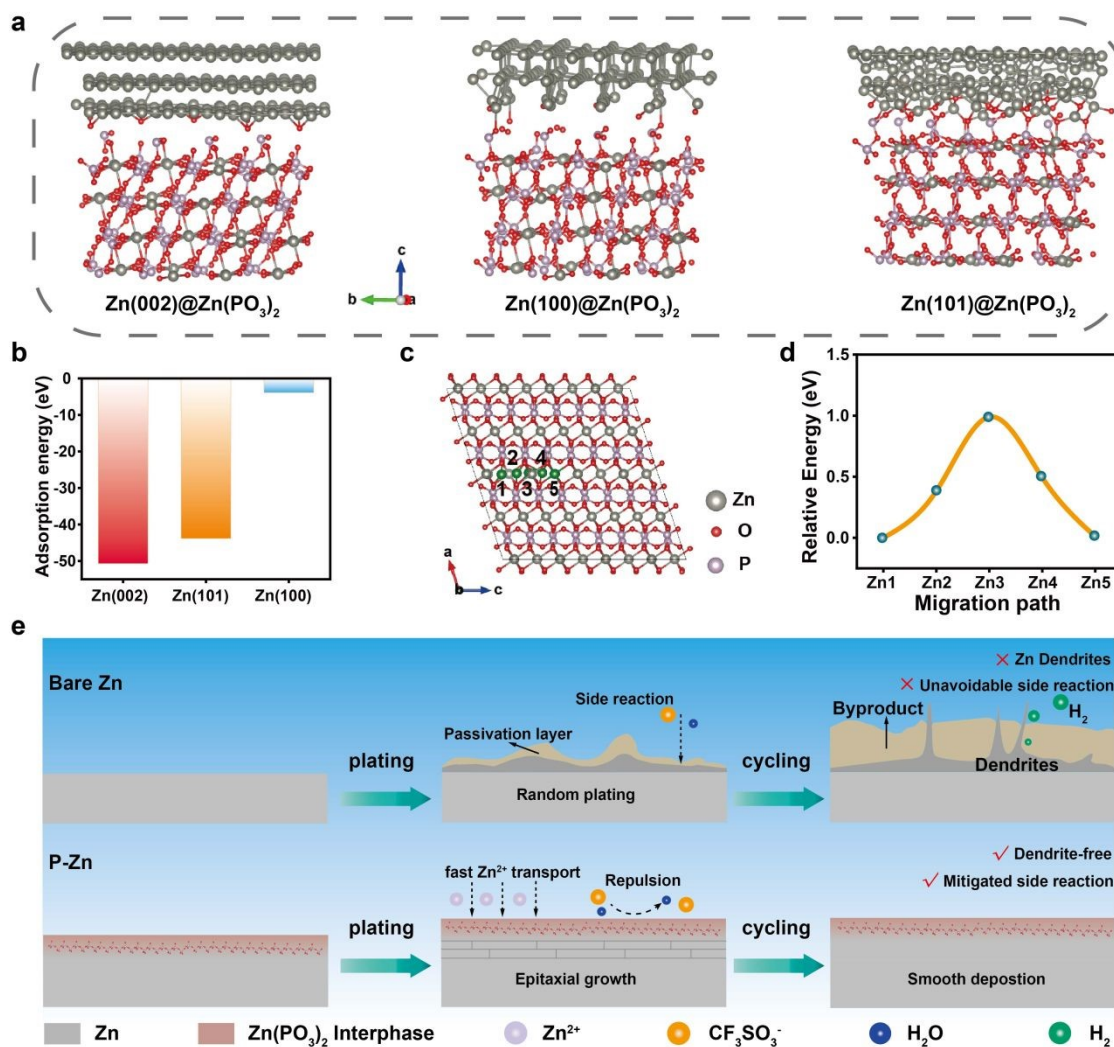



Fig. 4 (a) Adsorption models and (b) corresponding adsorption energy of different Zn crystal faces with the Zn(PO₃)₂ interphase. (c) First-principles calculations and (d) migration energy barrier of the optimum Zn²⁺ diffusion pathway A in the Zn(PO₃)₂ interphase. (e) The schematic illustration of the Zn deposition/stripping behaviour on the bare Zn and P-Zn electrodes.



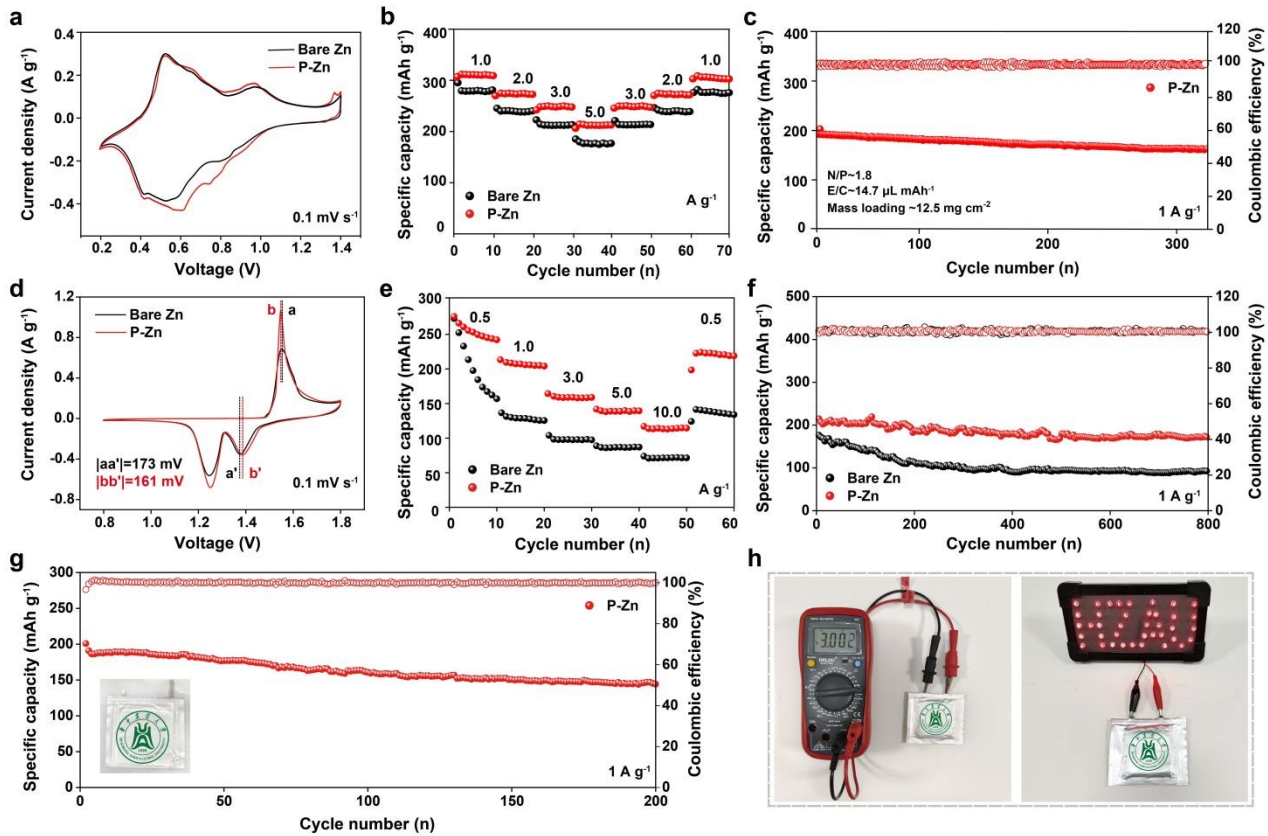


Fig. 5 (a) CV curves of Zn||NVO AZIBs at 0.1 mV s⁻¹. (b) Rate performances of the Zn||NVO AZIBs at various current densities. (c) Cycling performance at 1 A g⁻¹ with the low N/P ratio of 1.8. (d) CV curves of Zn||KMO AZIBs at 0.1 mV s⁻¹. (e) Rate performances of the AZIBs at various current densities. (f) Cycling performance of the AZIBs at 1 A g⁻¹. (g) Cycling performance of the AZIBs pouch cell at 1 A g⁻¹. (h) The illustration of laminated pouch cells.

The datasets used and analysed during the current study available from the corresponding author on reasonable request.

[View Article Online](#)[DOI: 10.1039/D5EB00098J](https://doi.org/10.1039/D5EB00098J)