

Materials Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. K. Panja, A. R. Patel, A. D. Fazal, T. D. Solanky, S. Dhibar and S. Kumar, *Mater. Adv.*, 2025, DOI: 10.1039/D5MA00750J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Recent Advances and Challenges in Graphene-Based Nanomaterials for Photocatalytic CO₂ Reduction

Abhishek R. Patel,¹ Anas D. Fazal,¹ Trupti D. Solanky,¹ Subhendu Dhibar,² Sumit Kumar,^{3*} Sumit Kumar Panja,^{1*}

¹Material Chemistry Laboratory, Tarsadia Institute of Chemical Science, Uka Tarsadia University, Maliba Campus, Gopal Vidyanagar, Bardoli-Mahuva Road, Surat-394350, Gujarat, India.

²Department of Physics, Indian Institute of Technology, Patna-801106, Bihar, India

³Department of Chemistry, Magadh University, Bodh Gaya-824234, Bihar, India

Abstract

Photocatalytic CO₂ reduction is a viable solar-driven approach to sustainably synthesize fuels and chemicals which provides great potential in response to the urgent threat of increasing atmospheric CO₂. Recently, graphene-based nanomaterials have arisen as extremely compelling platforms due to their large surface area, superior electrical conductivity and tunable electrical properties. This highlighted how new developments in graphene-based photocatalysts as CO₂ reduction including fundamental reaction mechanisms, thermodynamics, kinetics as well as light-induced charge separation. The presentation assessed different forms of grapheme (Graphene Oxide (GO), Reduced Graphene Oxide(rGO), doped graphene and 3D graphene) both with respect to their synthesis, functionality and the role of functionalization including for co-catalysts. Certain aspects of improved charge transport and catalytic activity are presented in the coupling of graphene with metal oxides, semiconductors, metals, carbon nitrides and Z-scheme systems. The review critically evaluates previous findings on the influence of differing synthesis methods on morphology, performance and included mechanistic information from spectroscopic and density functional theory (DFT) based studies. In addition to advances like single-atom catalysis, hybrid systems and machine learning based design, the review also discusses issues of catalyst stability, scalability and environmental issues. In the conclusion, future directions for developing graphene-based systems towards



effective, scalable and sustainable CO₂ photoreduction are also provided in the review.

Keywords: Photocatalysis, Graphene Oxide (GO), Reduced Graphene Oxide (rGO), CO₂ reduction; Charge transfer dynamics.

1. Introduction

Increasing levels of CO₂ in the atmosphere is an important factor associated with global climate change and presents a massive challenge to human and environmental systems [1]. CO₂ emissions have dramatically increased in the past century due to fossil fuel combustion, industrial processes and changes in land-use that have resulted in significant increases to global temperatures, extreme weather events as well as ocean acidification[2]. It is critical to reduce CO₂ levels in order to create better climate stability and ultimately sustainability [3]. Photocatalysis employs semiconductors to absorb light resulting in the formation of electron-hole pairs that drive cellular redox processes to convert CO₂ into hydrocarbons species such as methane, methanol and formic acids [4, 5]. Despite the interest surrounding this research, it is often obstructed by challenges surrounding conversion efficiency, poor selectivity and rapid recombination of photo-generated charge carriers.

Recently, graphene-based nanomaterials have attracted great attention as new components for photocatalytic systems [6]. Graphene-based materials in particular graphene and its derivatives, e.g., GO, rGO and functionalized hybrids have shown great potential to enhance photocatalytic performance based on a multitude of properties when compared to more traditional photocatalysts including the large surface area to mass ratio, high electron mobility, chemical stability/tolerance towards oxidation and ease of modification of surface chemistry [7, 8]. Graphene-based materials may enhance photogenerated charge separation, enhance light absorption spectra and improve CO₂ adsorption to overcome limitations in more traditional photocatalyst systems [9-11].

There is now considerable interest in investigating graphene-based nanomaterials for photocatalytic CO₂ reduction from the scientific community and we have already seen significant increases in publications and research activities in the past ten years.



Open Access Article. Published on 13 Hukuri 2025. Downloaded on 2025-11-18 07:30:13.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.


Interest in the area was less significant after 2015, though prior to that research on graphene-based photocatalysts were also pretty limited, more so in and around 2010[12, 13]. This largely came down to the outcome that the coupling of photocatalytic systems with graphene was a relatively new process and mechanism. As the researchers recognized the potential of the electrical properties, functionalities, large surface area and unique role as an electron mediator, the pressure to research increased. After the cumulative number of research papers on graphene in photocatalytic systems peaked around 2015, pressure again began to build due to global climate crisis challenges, with an especially high need for improvements in sustainable energy technology (to at least align in the same direction as work carried out in fulfilling the promise of advancements in hydrocarbon energy technologies). Newer syntheses, improved quality of graphene and hybrid photocatalysts between semiconductor materials (i.e., TiO_2 , $\text{g-C}_3\text{N}_4$) and MOFs, created new constructive waves in the research environment [14-16].

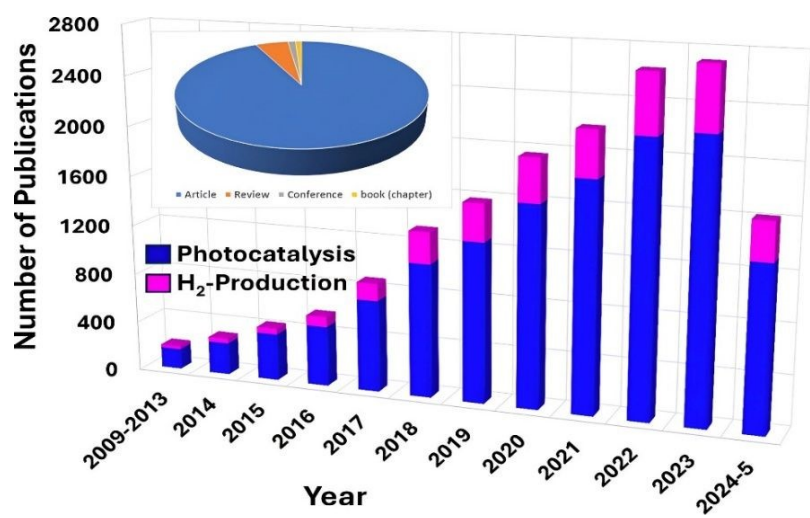


Fig. 1 Publications per year about graphene-based nanomaterials for photocatalytic reduction of CO_2 , Reprinted with the Ref. [17], copyright@2024, RSC.

In the past few years, the overall number of publications has generally gone up with a high frequency in high-quality journals in supplements with physics, chemistry and environmental engineering being the most prolific disciplines are due to the multidisciplinary nature (Fig.1). Overall, converging assumptions point towards a maturing technological state and teaching a collaborative approach to research devoted to using graphene and graphene nanostructures in purposeful experiences

containing photocatalytic reactions aimed at reduction for possible commercialization toward carbon neutral and carbon negative technologies.

This study reviews recent developments in graphene-based nanomaterials use in CO₂ reduction by photocatalytic processes. It reviews the different types of graphene composites and how they can enhance photocatalytic activity (and the scientific principles), addresses current challenges, compares performance between systems and discusses subsequent research avenues to advance this exciting subject into real-life and industrial applications.


2. Fundamentals of Photocatalytic CO₂ Reduction

2.1 Basic Principles and Reaction Mechanisms


To initiate redox reactions in the surface-driven, light-induced process of photocatalytic CO₂ reduction, semiconductors are used as photocatalysts that absorb photons.[18, 19] The photons excite electrons (e⁻) in the valence band (VB) to the conduction band (CB) as long as they have an energy equal to or greater than the bandgap energy (E_g) of the photocatalyst. When an electron is promoted to the CB, a hole (h⁺) is created in the VB and the VB is now positively charged.



The holes tend to participate in water oxidation to provide protons and maintain charge neutrality, while the photogenerated electrons can thermally decompose the significantly adsorbed CO₂ molecules [20, 21]. Depending upon the particular nature of the catalyst and reaction conditions, the reduction of CO₂ may follow a number of paths with potentially complex multi-electron transfer steps.



These reactions are thermodynamically uphill and require catalysts that can facilitate multi-electron processes with minimal energy input and shown in (Fig. 2) [20].



Open Access Article. Published on 13 Hukuri 2025. Downloaded on 2025-11-18 07:30:13.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

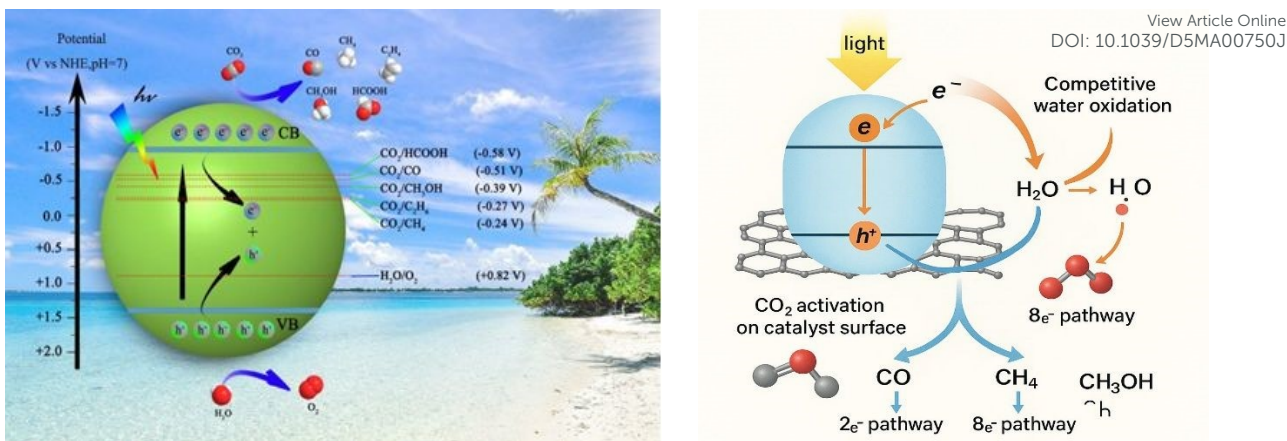


Fig. 2 (A) Band edge alignment and redox potentials for photocatalytic CO_2 reduction with H_2O , (B) General mechanism of graphene-based photocatalytic CO_2 reduction pathways, Reprinted with the Ref. [22], Copyright@2020, RSC.

2.2 Thermodynamics and Kinetics of CO_2 Photoreduction

CO_2 is a linear and stable compound with a strong C=O bond (bond energy of 750 kJ/mol) it is difficult to activate [23, 24]. Thermodynamic reductions of CO_2 to products such as CO, CH_4 or CH_3OH must overcome significant energy barriers and be utilized in conjunction with the redox potentials of the photocatalyst (**Fig. 3**). In terms of kinetic functionality, the pathway to CO_2 reductions competes with hydrogen evolution reaction (HER) which is often thermodynamically favourable [25].

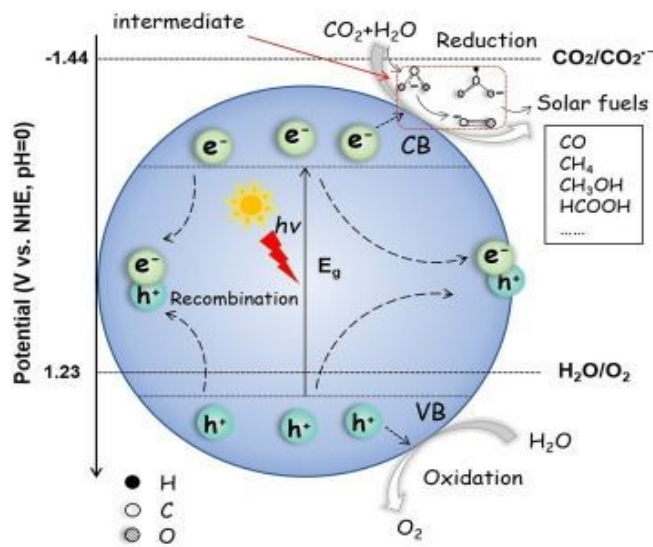



Fig. 3 Schematic Representation of Thermodynamics and Kinetics of CO_2 Photoreduction Reprinted with the Ref. [26], copyright@2020, Elsevier.

So, kinetic control through catalyst surface modification, active site engineering, and selective adsorption of CO_2 vs H^+ is important to increase selectivity [27]. Additionally, product formation is also very sensitive to the number of electrons transferred: CO and HCOOH are $2e^-$ products while CH_4 and CH_3OH are $8e^-$ and $6e^-$ products, respectively, making this kinetically more complicated.

2.3 Desired Products and Selectivity Control Reactions

Selectivity remains a central challenge in photocatalytic CO_2 reduction due to the coexistence of multiple reaction intermediates (COOH , CHO , CH_2OH) and competing reduction pathways that lead to diverse products [28,29]. Depending on the stabilization and transformation of these intermediates, the system can yield CO , HCOOH , CH_4 , or CH_3OH , which serve as valuable chemical feedstocks, hydrogen carriers or high energy density fuels. However, the intrinsic competition with the hydrogen evolution reaction (HER) and the difficulty in controlling electron-proton transfer steps often result in poor product distribution and low carbon efficiency. Consequently, improving product selectivity is not merely a matter of enhancing catalytic activity but also of directing the reaction mechanism toward well-defined and desirable pathways which is essential for practical applications in solar-to-fuel conversion.

A variety of strategies have been developed to enhance selectivity in CO_2 photoreduction. Catalyst composition and morphology play a pivotal role, where controlled doping with transition metals or nonmetals modulates electronic structures and adsorption energies, thereby stabilizing key intermediates and suppressing side reactions [30]. Similarly, rational engineering of the electronic band structure governs the separation and distribution of photogenerated charge carriers, influencing surface coverage and the reduction potential available for CO_2 activation [31]. Beyond intrinsic material properties, the introduction of surface functional groups provides specific anchoring sites that stabilize critical intermediates, improving the probability of their conversion into targeted products. In addition, external factors such as electrolyte pH, CO_2 partial pressure and the incorporation of co-catalysts can further tune reaction kinetics, facilitating selective product formation under optimized operating conditions [32].



Graphene-based materials have emerged as highly effective platforms for improving selectivity in CO₂ reduction owing to their unique physicochemical features. The conjugated π -network and superior electron mobility of graphene enable rapid charge transfer and efficient stabilization of electron-rich intermediates, thereby minimizing unwanted back-reactions. Furthermore, the tunability of graphene through heteroatom doping, covalent functionalization, and formation of heterostructures provides versatile pathways to modulate CO₂ adsorption strength and intermediate stabilization. These attributes, combined with graphene's ability to integrate synergistically with semiconductors and metal nanoparticles, make graphene-based photocatalysts promising candidates for achieving high selectivity toward desired products, thus offering a rational route toward efficient and sustainable CO₂-to-fuels conversion.

2.4 Role of Light Harvesting and Charge Separation

To use the photocatalytic process effectively, good light harvesting is important. Ideally, photocatalysts should absorb a wide spectral extent, especially in the visible region (~400–700 nm) where most solar energy is located [28, 29]. Many traditional photocatalysts (such as TiO₂) has large bandgaps (>3.0 eV) that prevents further efficient use of the sunlight [30].

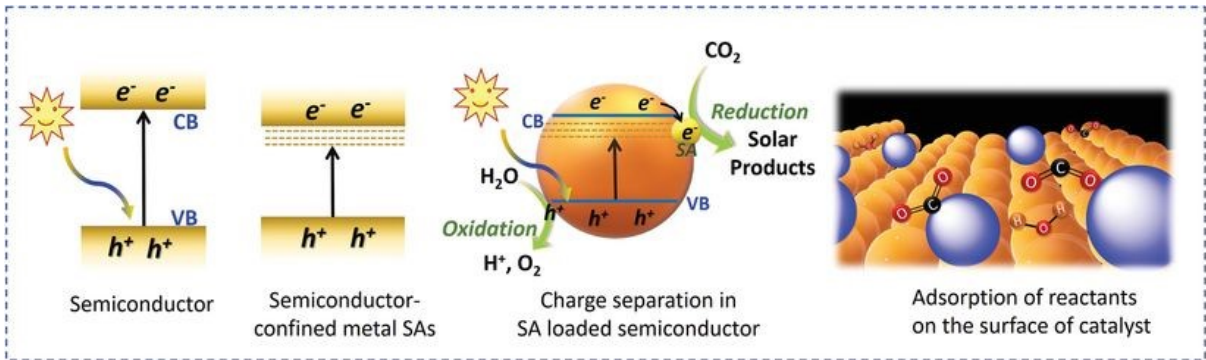


Fig. 4 Schematic Representation of light Harvesting and charge separation, Reprinted with the Ref [31], copyright@2020, Wiley Online Library.

Since photogenerated electron-hole pairs rapidly recombine and this can drastically reduce quantum efficiency, charge separation efficiency is thus also very important and shown in (Fig.4)[32]. The following are some strategies for increasing light absorption and reducing recombination. The overall performance of photocatalytic


systems is characterized by the synergy that can be established through increased light absorption, rapid charge carrier mobility and CO₂ adsorption on catalyst surfaces [33, 34].

2.4.1 Factors and areas of consideration

Bandgap engineering has been widely recognized as a fundamental strategy for improving photocatalytic CO₂ reduction efficiency. By tailoring the band structure, photocatalysts can extend their light absorption into the visible range while maintaining the redox potentials required for CO₂ activation and subsequent multi-electron transfer processes. Techniques such as heteroatom doping introduce impurity energy levels that narrow the bandgap and tune the electronic structure, while the construction of heterojunctions between semiconductors creates internal electric fields that facilitate charge separation. These modifications not only improve solar spectrum utilization but also influence the adsorption and stabilization of key intermediates, thereby enhancing both activity and selectivity. In particular, graphene-based heterojunctions with semiconductors provide unique advantages by integrating extended light absorption with efficient charge transport pathways.

Z-scheme photocatalytic systems represent another promising approach, drawing inspiration from the architecture of natural photosynthesis. In these systems, two semiconductors are coupled in a manner that preserves the strong reduction potential of one and the strong oxidation potential of the other, while photogenerated electrons and holes in the less energetic bands recombine internally. This spatial and energetic separation allows for simultaneous CO₂ reduction and water oxidation with high efficiency. Incorporating graphene into Z-scheme systems further enhances their performance, as graphene can act as a solid-state conductive bridge, promoting ultrafast charge transfer while suppressing recombination. Recent studies have demonstrated that such graphene-based Z-scheme systems exhibit superior stability and selectivity compared to conventional type-II heterojunctions, making them highly attractive for solar fuel production.

Surface plasmon resonance (SPR) effects associated with noble-metal decoration provide an additional avenue for enhancing photocatalytic CO₂ reduction. Metals such as Au, Ag, and Cu can generate localized electromagnetic fields under light



irradiation, leading to strong absorption in the visible region and the excitation of high-energy “hot” electrons. These hot carriers can be injected into adjacent semiconductors or graphene-based supports, where they participate directly in CO₂ reduction reactions. Moreover, the synergistic combination of plasmonic metals with graphene facilitates rapid hot-electron transfer due to the high conductivity and extended π -conjugation of graphene, thus suppressing charge recombination and improving reaction selectivity. Graphene itself also contributes by serving as an electron sink and conductive channel, enabling spatial charge separation across hybrid interfaces. Together, bandgap engineering, Z-scheme architectures, plasmonic enhancement, and graphene-mediated charge transport constitute complementary and mutually reinforcing strategies that can be rationally combined to overcome the efficiency and selectivity bottlenecks in photocatalytic CO₂ conversion. Although notable progress has been made with traditional photocatalysts for CO₂ reduction, their overall efficiency is still restricted by inherent challenges such as fast charge carrier recombination, narrow light absorption, and a limited number of surface-active sites for CO₂ activation. To overcome these drawbacks, researchers have increasingly focused on graphene and graphene-based nanomaterials, which offer outstanding electrical conductivity, large specific surface area, and chemically tunable interfaces. These features facilitate efficient charge separation and transfer, enhanced light harvesting when coupled with semiconductors, and improved catalytic reactivity. The subsequent section provides an in-depth discussion of the structure, properties, and photocatalytic roles of graphene and its derivatives in advancing CO₂ conversion technologies.

3. Graphene and Graphene-Based Nanomaterials

3.1 Structure and Properties of Graphene

Graphene is a 2D carbon allotrope made up of a single atomic layer of sp²-hybridized carbon atoms arranged in a honeycomb lattice and shown in (Fig. 5) [35]. This unique atomic arrangement gives graphene many exceptional physicochemical properties that make it a much-studied material with significant potential for a wide range of applications, including photocatalysis[36]. Logically, every carbon atom is connected

to three neighbours in graphene, forming a stable and delocalized π -electron system across the entire sheet [37]. The delocalization of electrons leads to the desired properties of graphene electroconductivity, thermal stability, and typical mechanical stability. For example, the intrinsic carrier mobility of graphene at room temperature is above $200,000 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$, with thermal conductivity beyond $5000 \text{ W m}^{-1} \text{ K}^{-1}$. Graphene also has excellent flexibility and only absorbs $\sim 2.3 \%$ of visible light, giving it apparent transparency, such as for optical electronic applications. It has the theoretical highest surface area: $2630 \text{ m}^2 \text{ g}^{-1}$ (simply meaning a large surface area for chemical reactions or adsorption).[38]

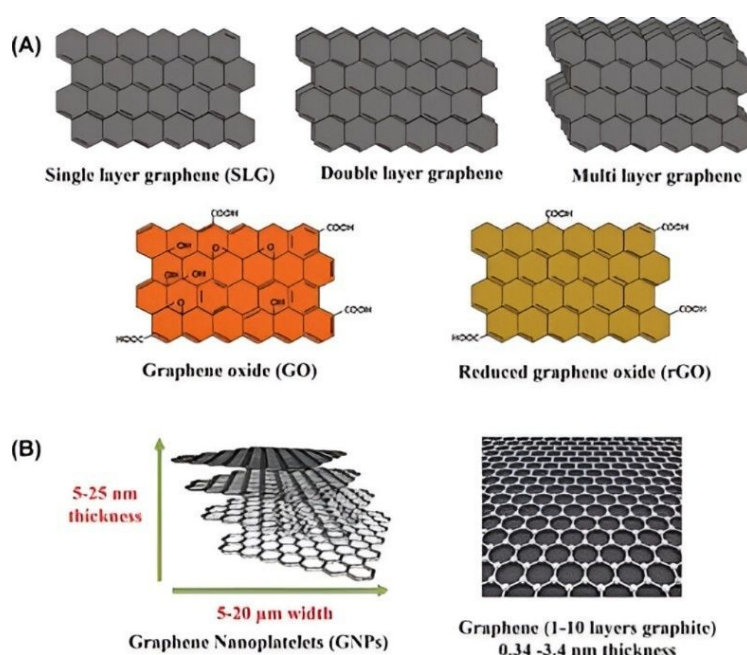


Fig. 5 A) Different structural forms of graphene and its derivatives: Single-layer graphene (SLG), Double-layer graphene, Multi-layer graphene, GO with oxygen-containing functional groups, RGO with partially restored graphitic structure (B) Morphological representations of graphene-based materials: Graphene nanoplatelets (GNPs) with 5–25 nm thickness and 5–20 μm lateral size, Few-layer graphene (1–10 layers) with thickness of 0.34–3.4 nm. Reprinted with the Ref. [39] copyright©2019, Dove Medical Press.

The unique characteristics make graphene a perfect medium for electron transport and interfacial charge transfer processes specifically, which is vital for photocatalytic processes [40]. However, pristine graphene is chemically inert, therefore lacks a bandgap which prevents it from being useful by itself in this area of electronics [41]. Therefore, researchers have looked into graphene-based derivatives and composites to both overcome the limitations of pristine graphene and take advantage of its conductive and mechanical properties.



3.2 Derivatives of GO, rGO, Doped Graphene, 3D Graphene

To prepare graphene for real photocatalytic and catalytic applications, numerous derivatives have been created [42]. The goals of the derivatives generally relate to introducing chemical functionalities, creating a bandgap, increasing dispersibility in solvents, and establishing synergistic effects with other catalytic materials[43].

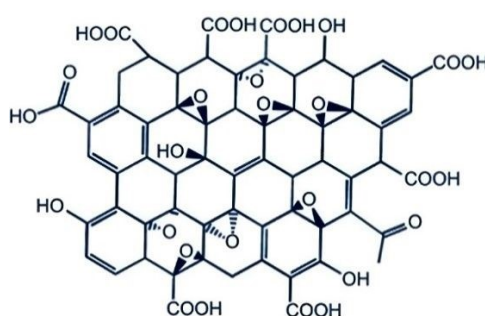


Figure: 6 Structural model of GO showing oxygen-containing functional groups such as hydroxyl (-OH), epoxy (-O-), carbonyl (C=O), and carboxyl (-COOH) groups distributed on the basal plane and edges of the graphene sheet. Reprinted with the Ref. [39]copyright@2019, Dove Medical Press.

GO is a heavily oxidized version of graphene, with many oxygen-containing functional groups (e.g., hydroxyl, epoxy, and carboxyl) attached to its sheet structure (Fig. 6). These oxygen-containing groups disrupt the conjugated π -electron system (cause π conjugation to cease), thereby diminishing the electrical conductivity of GO, but markedly increasing its hydrophilicity and chemical reactivity [44]. GO is easily dispersible in water, and other polar protic solvents, thereby permitting its use as an important scaffolding material to support subsequent growth and immobilization of photocatalysts [45]. Importantly GO when incorporated to make a composite material with photocatalysts, shows improved interfacial interactions, charge transfer and increased photocatalytic activity due to its higher density of functional groups and defect sites[46].


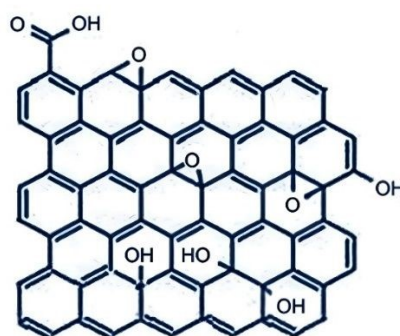


Fig. 7 Structural model of rGO, showing a partially restored sp^2 carbon network with residual oxygen-containing functional groups such as hydroxyl ($-OH$), epoxy ($-O-$), and carboxyl ($-COOH$) groups remaining on the basal plane and edges. Reprinted with the Ref. [39]copyright@2019, Dove Medical Press.

RGO can be chemically, thermally or electrochemically reduced GO leaving behind a partially restored π -conjugated network, some reduction in the oxygen content and the possibility of partially restoring GO electrical conductivity, making rGO a better candidate for electron mediator than GO itself [47]. The reduction also creates defects and residual functional groups that can impact interfacial properties and device performance. However, rGO provides a balance between good conductivity and sufficient surface functional groups, when surface functionality is important in encapsulating many photocatalytic systems (**Fig.7**)[48].

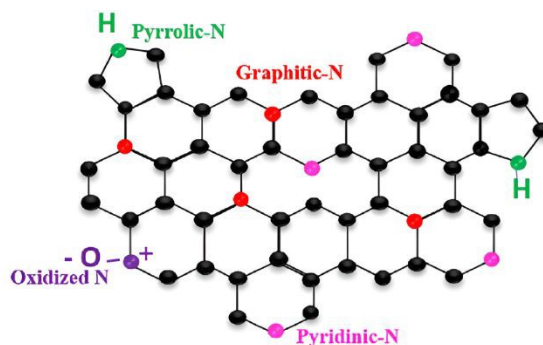



Fig. 8 Schematic representation of nitrogen-doped graphene showing different nitrogen configurations, including pyridinic-N, pyrrolic-N, graphitic-N, and oxidized-N within the graphene lattice. These doped sites significantly influence the electronic structure, surface reactivity, and catalytic activity of graphene-based materials, Reprinted with the Ref [49],copyright@2021, Springer.

Doped graphene is graphene with heteroatoms (like nitrogen (N), boron (B), sulphur (S) or phosphorus (P)) incorporated into the lattice as a substitution for carbon atoms or attached to the surface (**Fig. 8**). Doping creates changes in the electronic structure of graphene, creating localized states within the bandgap and changing work function of the graphene [50, 51]. For example, N-doped graphene has been shown to have better electron donor ability, so some of doped graphene's interactions increase catalytic reaction activity and lead to an increased interaction with nanoparticles of metals or semiconductors[52]. Each of these changes improve photocatalytic ability, through better charge separation and transfer.



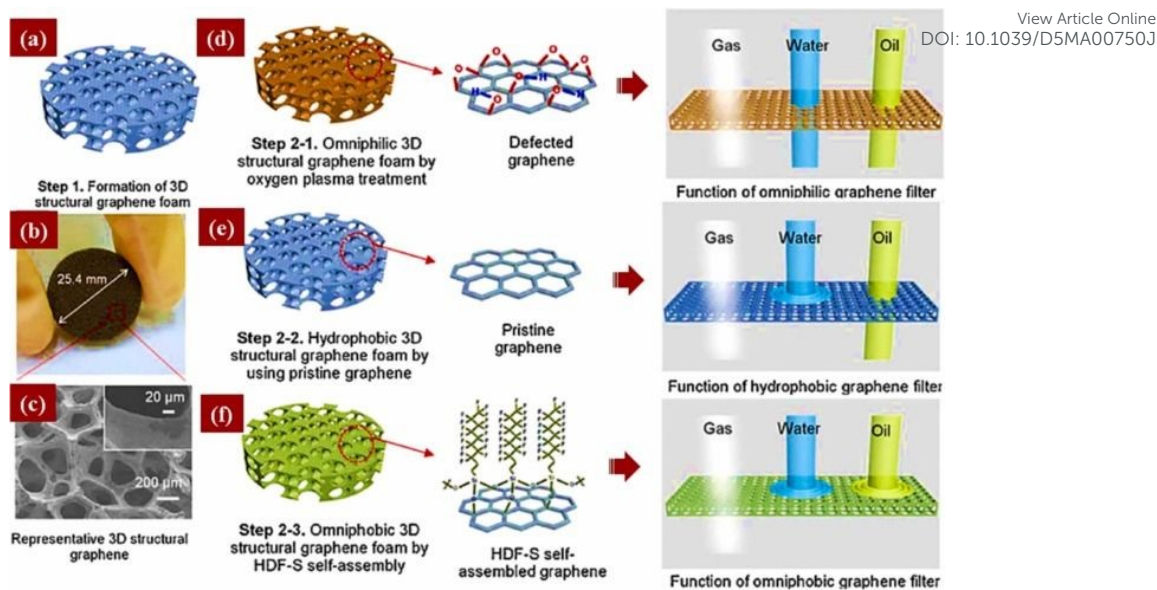



Fig. 9 Graphene foam contains a variety of various functional groups for use in the selective separation of gas, water, and oil. (a) Structure of graphene-foam. (b) 3D-graphene foam picture. (c) SEM-micrograph porous structures. (d) Gas, water, and oil travel through deformed graphene. (e) Pure graphene foam accepts gas and oil yet blocks water. (f) HDF-S-covalently bonded graphene can filter gases, Reprinted with the Ref [53], copyright©2018, Wiley Online Library.

Three-dimensional (3D) graphene architectures[54] (e.g., graphene aerogels, foams, and hydrogels) provide a macroporous and mesoporous scaffold, high surface area, significantly enhanced mechanical stability and favourable mass transport properties (Fig.9) [55-57]. These traits can be leveraged to support photocatalytic nanoparticles and encourage light absorption and reactant diffusion [46]. Furthermore, these 3D graphene support materials can provide continuous conductive pathways for charge migration, which will help reduce electron-holes recombination process.[56]

In general, these graphene-based nanomaterials can be intelligently chosen or designed based on the requirements of the photocatalytic system, for example, light absorption capabilities, charge transportation features, reactant adsorption and/or interfacial interactions.

3.3 Methods of Synthesis and Functionalization of Graphene and its derivatives

Graphene and its derivatives have unique physicochemical properties that can be synthesized and functionalized to enhance those properties and tailor them for specific applications[57]. This is particularly appropriate for photocatalysis for CO₂ reduction. Graphene synthesis is separated into two major categories - top down and bottom up (Fig.10) [58].

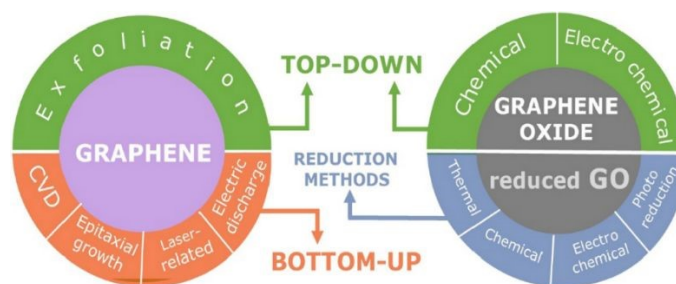

View Article Online
DOI: 10.1039/D5MA00750J

Fig. 10 Methods of Synthesis and Functionalization of Graphene and its derivatives, Reprinted with the Ref [59], copyright@2022, Springer.

The **top-down** method involves the exfoliation of bulk graphite into single individual graphene sheets [60]. Mechanical exfoliation can produce high quality graphene, but is not scalable. Chemical exfoliation methods, like the Hummers method and its variations, are often employed for GO synthesis. Chemical exfoliation uses powerful oxidizing agents (e.g. KMnO_4 , H_2SO_4) in the oxidation of graphite adding oxygenated groups which separate the interlayers and promote exfoliation. The GO produced can then be reduced to rGO via chemical (e.g. hydrazine, ascorbic acid), thermal, or electrochemical routes[61].

Bottom-up methods use graphene from molecular precursors, generally through chemical vapor deposition. Chemical vapor deposition puts graphene films into high purity, large-area films on metal substrates (Cu or Ni) [62]. CVD has great potential in different electronic and optoelectronic applications, but it is not considered practical for the production of graphene based photocatalytic composites due to cost and scalability [59].

The functionalization of graphene is needed to bring usable chemical groups, improve compatibility with other materials, and ultimately improve electronic properties[63]. Covalent functionalization takes place when chemical groups bond to the carbon lattice (often through reactions with the oxygenated groups in GO, for example), provides stable bonds and improved dispersibility for composites; however, this process may limit the use of the conjugated structure of graphene and limit conductivity. Non-covalent functionalization generally introduces molecules or nanoparticles from the enveloping compound to the sp^2 framework of graphene through π - π interactions, hydrogen bonding and/or electrostatic interactions[64, 65].



In photocatalytic applications, functionalization strategies usually consist of decorating graphene with metal or metal oxide nanoparticles (TiO_2 , ZnO or CdS); anchoring co-catalysts; or doping with heteroatoms to improve the potential of light absorption, reactive sites and to improve charge separation [66]. Generally, methods of synthesis/functionalization are the major factors in impacting the overall performance of the graphene-based composites synthesized.


3.3.1 Chemical synthesis methods for graphite oxide

Extensive research has focused on understanding the structure of GO, the primary precursor for graphene materials. GO is typically synthesized by intercalating and oxidizing graphite powder using strong acids (e.g., HCl , H_2SO_4 , HNO_3) and oxidizing agents (e.g., NaNO_3 , KMnO_4 , KClO_3). Several chemical synthesis methods (also see Table 1) discussed below. Each method differs in its oxidants, advantages, disadvantages, and resulting carbon-to-oxygen (C/O) ratios.

Brodie's oxidation method was the first to synthesize GO by reacting graphite with KClO_3 along with HNO_3 at around 60°C for three to four days.[67, 68] The process involved repeated oxidation steps and drying at 100°C . Although effective, it has major drawbacks, including long reaction times and the emission of toxic gases.

Staudenmaier method improved Brodie's process by using a mixture of concentrated HNO_3 , H_2SO_4 , and gradually added KClO_3 to achieve higher oxidation in a single vessel.[69] The reaction involved controlled heating, stirring, and subsequent cooling with water, which is followed by filtration and washing. It produces highly oxidized GO but major disadvantages are long reaction times, explosion risks, and toxic chlorine gas release.

Original Hummer's method introduced a faster and safer alternative for synthesizing GO using KMnO_4 and NaNO_3 as oxidants in conc. H_2SO_4 with graphite.[70] The reaction proceeds through controlled temperature stages ($0-4^\circ\text{C}$, 35°C , and 98°C). It takes about two hours. After oxidation, H_2O_2 is added to reduce residual manganese compounds, followed by washing and drying to obtain GO. The mechanism involves four stages, which are Intercalation, Convection-diffusion, Oxidation and Purification. During Intercalation, H_2SO_4 and NaNO_3 generate HNO_3 and reactive oxygen species that open graphite layers. KMnO_4 reacts with H_2SO_4 to form Mn_2O_7 , which




intercalates between layers in the step of Convection-diffusion. Further, Mn_2O_7 decomposes into O_2 and O_3 , oxidizing graphite into graphite oxide. The purification is performed using H_2O_2 and HCl , it removes residual manganese compounds. Improved Hummers methods aim to enhance the efficiency, yield, and environmental safety while reducing toxic emissions. These modifications fall into several main categories.

$\text{H}_2\text{SO}_4/\text{KMnO}_4$ -based methods eliminates NaNO_3 , preventing toxic $\text{NO}_2/\text{N}_2\text{O}_4$ release without reducing yield.[71] It enables large-scale, eco-friendly GO synthesis, with oxidation levels adjustable by KMnO_4 concentration and drying temperature. H_2O_2 acts as a terminating agent, and its quantity influences the C/O ratio. The reaction involves three stages: acid intercalation, oxidation to pristine graphite oxide, and hydration to form GO. A “mild oxidation” variant (lower KMnO_4 ratio) yields more crystalline, water-dispersible GO suitable for high-conductivity graphene.

Introduced by Marcano et al., $\text{H}_2\text{SO}_4\text{--H}_3\text{PO}_4/\text{KMnO}_4$ -based methods replace NaNO_3 with a 9:1 $\text{H}_2\text{SO}_4\text{:H}_3\text{PO}_4$ mixture, increasing oxidation efficiency and yield while eliminating toxic gas formation.[72] It allows better temperature control (35–50 °C) and produces three times more GO than the original method. Further optimization studies refined intercalators and drying steps for faster, cost-effective, and scalable production.

In case of Ferrate-assisted oxidation, KMnO_4 is partially replaced with K_2FeO_4 , which has higher oxidizing power and operates under milder conditions (<5 °C, 35–95 °C), improving efficiency while reducing acid use and environmental impact. During KMnO_4 -free methods, Eco-friendly alternatives, such as K_2FeO_4 , ozone, peracetic acid, and electrochemical oxidation, avoid toxic manganese by-products. Though oxidation levels may be lower, these methods offer safer, scalable production routes. Microwave-assisted oxidation approach rapidly heats reactants via dielectric heating, reducing synthesis time from several days to about 20 minutes at 100 °C. It yields GO with higher C/O ratios (less oxygenated) but is significantly faster and energy-efficient.[73, 74]

3.4 Graphene as an Electron Mediator and Co-Catalyst



Graphene-based nanomaterials are essential electron mediators and co-catalysts in the context of photocatalytic CO₂ reduction and photocatalysis processes (**Fig. 11**). Both roles are important for charge separation, interfacial charge transfer, and the recombination suppression of photogenerated electron-hole pairs[75]. As an electron mediator, graphene illustrated an effective electron transport pathway between the photocatalyst and the reaction interface[76]. The high electrical conductivity of graphene and its massive π -conjugated system allows excited electrons to readily transfer from a semiconductor photocatalyst to graphene, a charge sink or electron reservoir, to prevent holes recombination and remain energized carriers[77]. In TiO₂/graphene composites, for example, photogenerated electrons can migrate away from TiO₂ to graphene and, subsequently, to CO₂ molecules disposed on the surface, providing for multi-electron reductions. The unique capacity of graphene produced directional charge flow allowing for the increase in the overall quantum efficiencies the system[78, 79].

Graphene serves as a support co-catalyst that supplies active sites for adsorption and activation of CO₂ and other materials (**Table 1**). Functional groups, defects, or impurities (dopants) in the graphene surface can serve as anchoring sites or functional catalytic sites [76]. For example, in nitrogen-doped graphene, the lone pair electrons of nitrogen can react with CO₂ and catalytically activate and reduce it[78]. Metal nanoparticles deposited onto graphene, and the support themselves, can work together to enhance catalytic activity. The electron rich graphene substrate can stabilize metal active sites, facilitate charge transfer, and modulate the electronic environment of the catalytic centres.


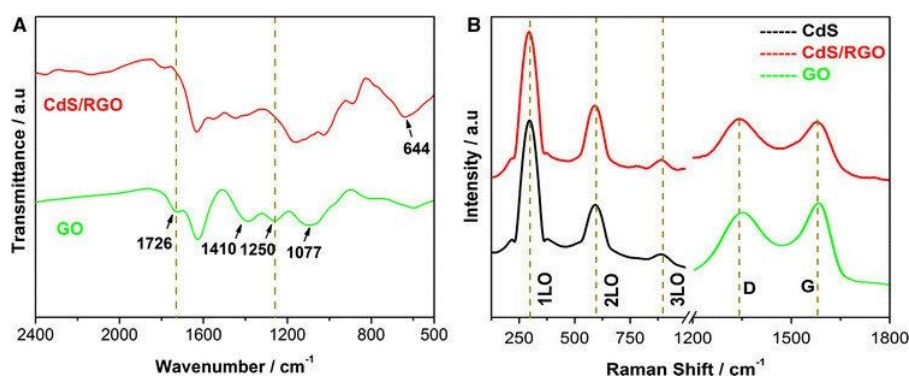


Fig. 11 (A) FT-IR-profiles of GO and CdS-RGO (B) Raman-spectra of GO-CdS-nanoparticles-and-CdS-RGO, Reprinted with the Ref [80], copyright@2020, Springer.



Graphene composites with semiconductors can form a Schottky junction or heterojunction, which facilitates charge separation and selective pathway for reaction. CdS/rGO systems provide an example, where rGO facilitates the charge process by improving mobility of the electrons and also minimizing the photo corrosive degradation of CdS material. Similarly, graphene composites with perovskites improves electron transport enhancing rapid electron transport potential, stability, and superior photocatalytic performance[75, 81].

Table 1: Summary of synthesis methods and their impact on catalytic performance

SN.	Synthesis Method	Typical Procedure	Surface Area	Defect Density	Impact on Catalytic Activity	Remarks	Ref.
1	Hummers' Method (Chemical Oxidation/Reduction)	Oxidation of graphite → Graphene oxide → Reduction to rGO	Moderate-High (depends on reduction)	High (due to oxygen functional groups, vacancies)	Enhances active sites and electron transfer but may introduce recombination centers	Common, scalable; quality depends on reduction degree	[82]
2	Hydrothermal/Solvothermal	Graphene oxide mixed with precursors, treated at high T & P	High (porous, few-layer structures)	Moderate (controlled defect formation)	Good dispersion of co-catalysts, strong interfacial contact improves activity	Suitable for hybrids (e.g., graphene-metal oxides)	[83]
3	Chemical Vapor Deposition (CVD)	Hydrocarbon gases decomposed on metal substrate	Very High (high crystallinity, large domain size)	Low (near defect-free)	Excellent charge transport; but fewer catalytic sites unless doped/functionalized	Expensive, limited scalability	[84]



4	Exfoliation (Liquid phase or Electrochemical)	Sonication, shear, or electrochemical delamination of graphite	Moderate-High (depends on exfoliation efficiency)	Variable (controlled via process)	Balances conductivity and defect density, useful for heterojunctions	Green methods possible; lower yield than chemical oxidation	[85]
5	Doping-assisted synthesis (N, S, B, P doping)	Graphene prepared with heteroatoms introduced during synthesis or post-treatment	Moderate	Controlled defect sites (heteroatom-induced)	Creates active sites, improves CO ₂ adsorption and electron transfer	Strongly enhances selectivity for CO/CH ₄	[86]

4. Recent Progress in Graphene-Based Photocatalytic Systems

Graphene-based materials can benefit photocatalytic systems and help reduce CO₂ levels. When combined with different functional materials, such as metal oxides, semiconductors, metals and carbon-based materials, they can result in advanced nanocomposites with better charge separation, light absorption capacity, and surface reaction sites [87, 88]. This section will talk about the recent developments in these five fields: graphene/metal oxide nanocomposites, graphene/semiconductor heterojunctions, graphene/metal-based nanohybrids, graphene/carbon nitride and their 2D/2D heterostructures, and graphene-based Z-scheme photocatalytic systems[89, 90].

4.1 Graphene/Metal Oxide Nanocomposites

Metal oxides are some of the most studied photocatalytic materials due to their advantageous band structures, photostability, and availability, including tungsten trioxide (WO₃), zinc oxide (ZnO), and titanium dioxide (TiO₂) (Fig. 12) [91]. Unfortunately, the fast recombination of photogenerated charge carriers and the limited visible light absorption often decreases the actual photocatalytic performance of metal oxides. One successful strategy to overcome these limitations has been to



combine these systems with graphene[92]. Graphene/metal oxide nanocomposites have emerged as highly effective photocatalytic systems owing to the synergistic effects facilitating charge separation, light absorption, and surface reaction kinetics[93]. In these nanocomposites, graphene behaves as a conductive support and electron mediator, and metal oxides are the primary photocatalysts. Graphene in combination with TiO_2 , ZnO , Fe_2O_3 , and CuO not only improves photocatalytic performance in CO_2 reduction under UV light, but also performs well in visible light[94, 95].

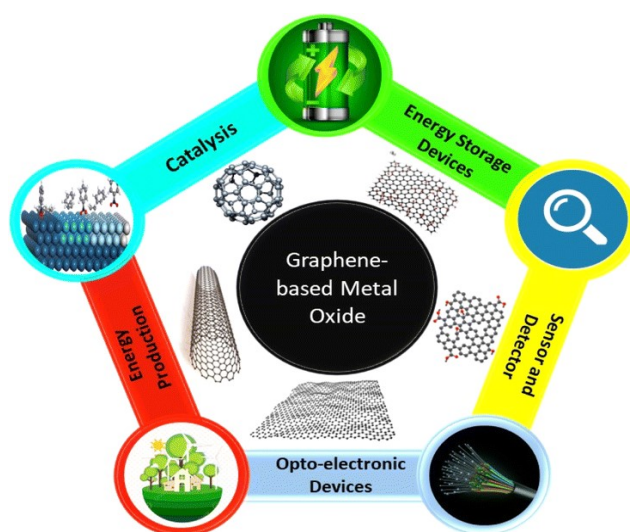


Fig. 12 Nanocomposites of Graphene/Metal Oxide, Reprinted with the Ref [96], copyright@2024, RSC.

Graphene/ TiO_2 has been studied more than most other systems. Graphene is critical to improving the photocatalytic efficiency of TiO_2 , as it increases light absorption in the visible area and reduces electron-hole recombination[97, 98]. However, due to the high electron mobility and high surface area of graphene, electrons can be transferred quickly from the TiO_2 conduction band to a graphene sheet to lengthen the life of photogenerated charge carriers. In addition, graphene has multiple active sites for CO_2 adsorption, which is important for increasing photocatalytic conversion efficiency[99, 100].


Graphene enhances the CO_2 photoreduction activity of many ZnO -based nanocomposites. It is said that the graphene sheets intercalate and transport electrons from the heated ZnO which reduces charge-recombination and improves the production of the key intermediates CO_2^- and HCOO^- [101-104]. Because of its π -



conjugated electronic framework, graphene can produce enhanced interactions with CO₂ through π - π stacking allowing for improved gas collection and activation on its surface[105]. Graphene also enhances the photocatalytic activity of other visible-light responsive metal oxides such as Fe₂O₃ and CuO. Overall, the charge transport, and increased absorption of light energy that is seen in graphene/Fe₂O₃ composites comparatively to Fe₂O₃ was likely due to the small bandgap of Fe₂O₃[106]. Graphene performs similarly in the case of CuO as well since the heterojunction also has a considerable charge transport factor while stabilizing reactive species for the CO₂ reduction pathways[107].

The synthetic methods including hydrothermal synthesis, sol-gel procedures and in situ growth are important factors that affect interfacial contact, particle size distribution and electron coupling between graphene and metal oxides. Efficient charge transport through the nanocomposite is dependent on creating strong interfacial contacts that optimize electron transport pathways and facilitate lower energy barriers for charge migration[108, 109]. Graphene/metal oxide nanocomposites are versatile photocatalysts that may be engineered for higher CO₂ conversion performance, by tailoring materials design i.e., composition, shape, and interfacial properties in unprecedented detail.

Some recent studies have further highlighted the importance of rational design strategies in advancing photocatalytic systems for energy and environmental applications (**Table 2**). ZnO-based heterostructures continue to attract attention due to their cost-effectiveness and stability, though their intrinsic drawbacks necessitate heterojunction engineering [110]. Both S-scheme and Z-scheme heterostructures have demonstrated exceptional improvements in charge separation and redox capability, with Nb₂O₅/La₂O₃ and ZnO-g-C₃N₄-CuO systems showing outstanding hydrogen evolution rates and strong stability.[111-113] Similarly, the integration of CNTs with Sr-doped ZnO and the ternary ZnO-Cu-CdS composite reveal that synergistic effects between dopants, carbon supports, and mediators such as Cu can significantly enhance light absorption, interfacial charge transfer, and pollutant degradation.[112, 114] These advances not only improve photocatalytic efficiency but also broaden



application versatility, spanning H₂ production, dye degradation and CO₂ reduction.[115]

541


542 **Table: 2** Comparative performance of graphene-based photocatalysts for CO₂ reduction

SN	Catalyst System	Synthesis Method	CO ₂ Conversion Rate	Product Selectivity	Quantum Efficiency (QE)	Stability (h)	Ref.
1	rGO-TiO ₂ nanocomposite	Hydrothermal assembly (GO + Ti precursor)	~45–80 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CO (70%), CH ₄ (20%), H ₂ (10%)	0.5–1.2%	15–20 h	[116]
2	Graphene-ZnO heterojunction	Solvothermal growth of ZnO on GO	~30–60 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CO (65%), CH ₄ (25%)	0.3–0.8%	10–15 h	[117]
3	N-doped Graphene-Cu ₂ O	In-situ reduction with nitrogen precursor	~120 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CH ₄ (55%), CO (40%)	~2.1%	30 h	[118]
4	Graphene-g-C ₃ N ₄ 2D/2D heterostructure	Thermal polymerization of urea + GO	~150 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CO (80%), CH ₄ (15%)	~2.5%	40 h	[119]
5	rGO-Ag-TiO ₂ plasmonic system	Photo deposition of Ag NPs on rGO-TiO ₂	~200 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CO (90%), trace CH ₄	~3.0%	50 h	[120]
6	Graphene-MoS ₂ hybrid	Hydrothermal co-assembly	~100 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CO (75%), CH ₄ (20%)	1.8%	25 h	[121]
7	B-doped Graphene-TiO ₂	Sol-gel with boron precursor	~85 $\mu\text{mol g}^{-1} \text{h}^{-1}$	CH ₄ (60%), CO (30%)	1.0–1.5%	20 h	[122]

543

544 4.2 Graphene/Semiconductor Heterojunctions

545 Besides the classic metal oxides, graphene has been paired with a number of
 546 semiconductors with lower band gaps and tunable properties to generate competitive
 547 photocatalytic heterojunctions[123, 124]. There have been a large number reporting
 548 the hybridization of graphene with the semiconductor's bismuth vanadate (BiVO₄),
 549 molybdenum disulphide (MoS₂), cadmium sulphide (CdS), and graphitic carbon
 550 nitride (g-C₃N₄) along with hybrid hierarchically porous catalytic metal oxides where
 551 the changing properties to metal oxides were complimentary as shown in (Fig.13)
 552 [125].



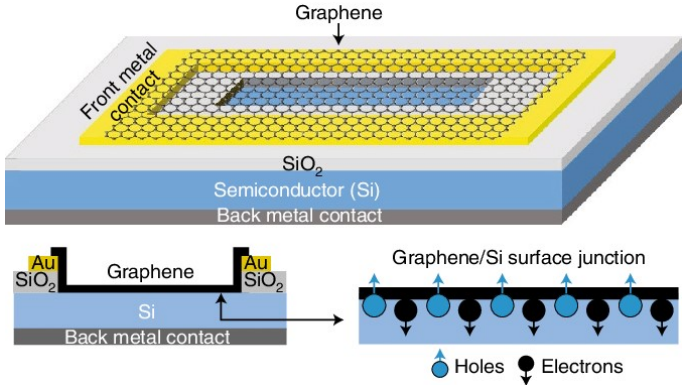


Fig:13 Schematic of a graphene on-semiconductor Si heterojunction photovoltaic cell Top,
Reprinted with the Ref [126], copyright@2019, Nature.

Kim et al. successfully synthesized ZnO nanostructures with nanoneedle and nanowall morphologies directly on few-layer graphene sheets.[127] In their approach, mechanically exfoliated graphene was transferred onto SiO₂/Si substrates, followed by the growth of ZnO using a metal-organic vapor phase epitaxy (MOVPE) process carried out without any catalyst assistance. The study revealed that both the aspect ratio and spatial arrangement of the ZnO nanostructures – whether aligned vertically or organized in rows – were strongly influenced by the growth temperature, which affected nucleation behavior at the step edges of the graphene surface. Furthermore, the optical characteristics of the ZnO/graphene hybrids were examined through photoluminescence (PL) spectroscopy conducted in the 17–200 K temperature range, providing insights into their structural and electronic quality.

Zinc sulfide (ZnS), one of the earliest studied semiconductors, shares structural and electronic similarities with ZnO but offers distinct advantages such as wider band gaps (3.72 eV for cubic and 3.77 eV for hexagonal forms), making it ideal for UV-selective optoelectronic applications like photodetectors and sensors.[128, 129] Although various low-dimensional ZnS nanostructures have been synthesized, systematic studies on ZnS nanostructure arrays have only recently advanced, unveiling new opportunities to exploit their unique properties.[130] Furthermore, growing research on ZnS-graphene nanocomposites highlights the synergistic interaction between the two materials, leading to improved photocatalytic and electronic performance.

4.3 Graphene/Metal-based Nanohybrids



Photo-corrosion represents a significant limitation to direct bandgap semiconductors like CdS (~2.4 eV) which have relatively good properties for visible spectrum light harvesting. Beyond stabilizing the photocatalyst, encapsulating CdS with graphene would help with charge separation[131]. Acting as an electron sink, graphene minimizes recombination losses and improves durability, by lowering operating rates while light is present. The CdS/graphene systems have experienced promising CO₂ reduction rates and high quantum yields[132].

Another layered semiconductor with better catalytic properties and hydrogen evolution properties is MoS₂[133]. When combined with graphene, MoS₂ can reduce CO₂ by facilitating charge transfer and providing extra edge sites[134]. MoS₂/graphene composites demonstrate high rates of conversion of CO₂ to CH₄ when exposed to visible light and the fact that they are hybrids ensures good interfacial contact and effective separation of photogenerated carriers[135].

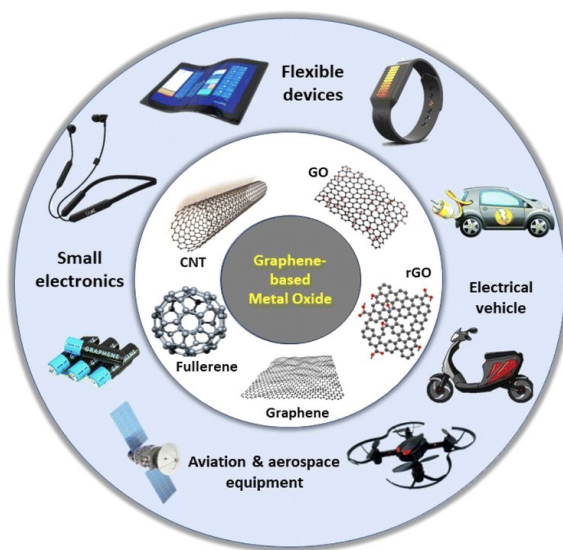


Fig. 14 Graphene/Metal-based Nanohybrids, Reprinted with the Ref [96], copyright@2024, RSC.

In order to solve cost issues, the incorporation of accessible non-noble metals (Ni, Co, Cu) has emerged[136]. These metals are catalytic, and have adequate proximity to graphene, and increased efficiencies of electron transport pathways. Ni/graphene composites provide enhanced CO₂ adsorption and activation abilities, making them appealing candidates for photoreduction applications[137]. Co and Cu NP's help support the dynamics of charge carriers while also participating in multi-electron



Open Access Article. Published on 13 Hukuri 2025. Downloaded on 2025-11-18 07:30:13.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.


transfer processes[138].In metal type nanohybrids shown in (Fig.14), graphene functions as a conductive support medium and as a functional medium to stabilize metal particles, limit aggregation, and manipulate electrical properties at the interface, thus improving photocatalytic performance[139].

4.4 Graphene/Carbon Nitride and 2D/2D Heterostructures

2D/2D heterostructures of graphene and other two-dimensional materials provide a new architecture to help in photocatalysis as shown in (Fig.15). In a layered composite format, conducive photocatalytic CO₂ conversion occurs because composites allow improved proximity, faster charge transport, and light absorption [140].

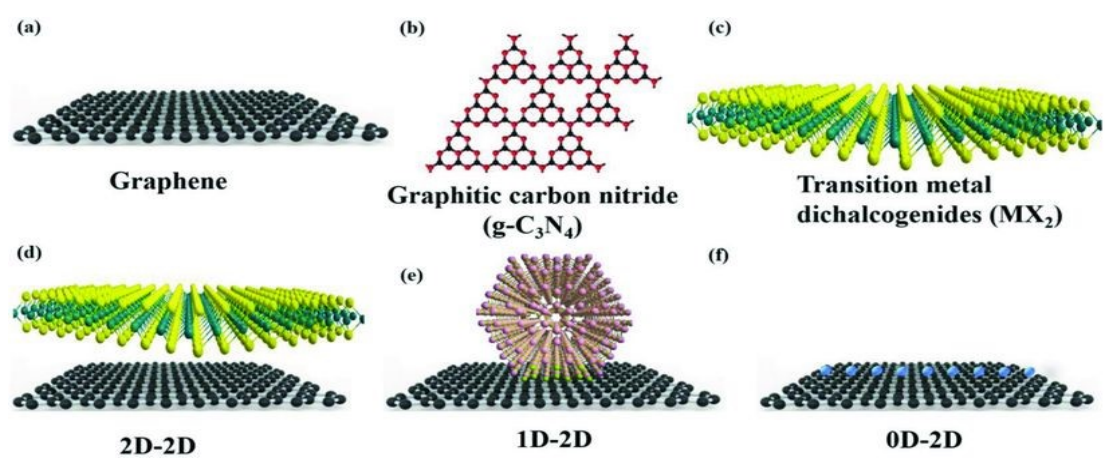


Fig. 15 Frontiers of 2D-materials used in catalysis and their heterostructures, Reprinted with the Ref [141], copyright@2019, Wiley Online Library.

Graphene/g-C₃N₄ 2D/2D heterostructures represent a new area of interest due to their synergistic properties. g-C₃N₄ absorbs visible light and has photocatalytic activity, while graphene has solid-state conductivity and promotes charge transport[142]. Thus, a combination of these material properties provides substantial improvements to the standard photocatalytic performance observed in methane and methanol yields under simulated solar light exposure. Other two-dimensional materials, such as MoS₂, WS₂, and layered double hydroxides (LDHs), have been used as van der Waals heterojunctions with graphene[143]. These heterojunctions improve charge separation with electric fields formed in-plane and overlapping conduction and/or valence bands[144]. A heterojunction of MoS₂/graphene hybrid

superstructures improves CO_2 reduction reaction activity and stability because the edges of MoS_2 form catalytic sites and graphene is a very effective conductor[145]. The very thin dimension of 2D materials generates a high surface-to-volume ratio, resulting in a greater density of exposed active sites, drastically reduces the charge diffusion distances, and has the potential to improve CO_2 and photoreduction kinetics, but facilitates coupling to light-harvesting systems like sensitizers and dyes[146, 147].

4.5 Graphene based Z-scheme Photocatalytic Systems

Z-scheme systems incorporate two semiconductors to accomplish efficient charge separation while utilizing both reduction and oxidation potentials, simulating natural photosynthesis as shown in (Fig.16) [148]. In Z-scheme transistor topologies, graphene has been and is used as an electron mediator, allowing for fast electron transport and therefore improved charge carrier dynamics[149]. In traditional Z-scheme processes with two semiconductors, a redox mediator physically connects two semiconductors with semi-ideal band alignment and free charge movements and generates problems of low efficiencies and back reflexes[150]. For example, graphene facilitates electron transfer from $\text{g-C}_3\text{N}_4$ to TiO_2 pigment so that the redox potentials stay high and the photocatalytic efficiency of the CO_2 photoreduction products improves[151, 152].

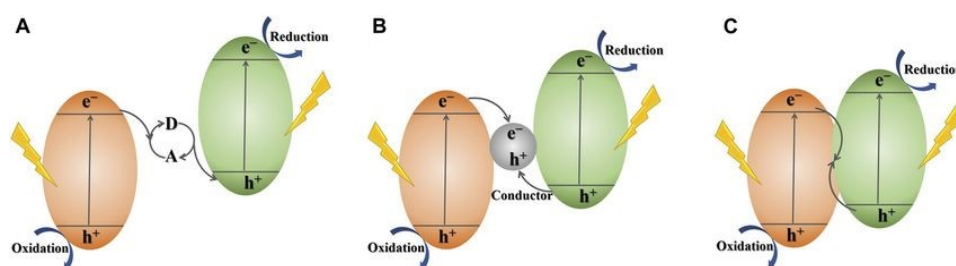


Fig. 16 Schematic illustration of different types of Z-scheme photocatalytic systems: (A) traditional Z-scheme photocatalytic system, (B) all-solid-state Z-scheme photocatalytic system, (C) direct Z-scheme photocatalytic system, Reprinted with the Ref [153], copyright@2024, Frontiersin.

There have also been dual-component systems that involve graphene improving the interfacial contact, as well as reducing direct charge recombination, such as $\text{BiVO}_4/\text{Graphene}/\text{g-C}_3\text{N}_4$ and $\text{CdS}/\text{Graphene}/\text{ZnIn}_2\text{S}_4$. These arrangements utilize



the conductive pathway of graphene in order to create directed charge flow, which enhances quantum efficiencies and product yield[154].

In addition, heterojunctions are more structurally robust when supported with graphene allowing for greater resistance to changing environmental situations[155]. High rates of CO₂ reduction have become achievable due to the wide variety of applications humans have created for such designs, particularly under visible to solar light[156]. All and all, Z-scheme graphene-based systems are a complex photocatalytic architecture which should promote reduction and charge recombination losses while maximizing light harvesting and redox potential. The potential for these to scale up solar to fuel technology is exciting[157-161].

In recent years, various other graphene-based composites have emerged as highly efficient photocatalysts for CO₂ reduction owing to their superior conductivity, large surface area, and ability to promote charge separation. A concise summary of representative systems, their photocatalytic performance, and the resulting products is presented in **Table 3**.

Table: 3 Overview of CO₂ photocatalytic conversion into solar fuels and value-added chemicals using graphene-based composite photocatalysts

Composite photocatalyst	Light source	Reaction medium	Main products	Photocatalytic performance	[Ref.]
Graphene-WO ₃ nanobelt composite	Xenon lamp, 300 W	CO ₂ and gaseous H ₂ O	CH ₄	Conversion rate: 0.89 μmol h ⁻¹ (after 8 h of irradiation)	[162]
ZnIn ₂ S ₄ /N-graphene	Xenon lamp (300 W)	84 mg NaHCO ₃ , 2M H ₂ SO ₄	CO, CH ₃ OH, CH ₄	CH ₄ : 1.01 μmol h ⁻¹ g ⁻¹ CO: 2.45 μmol h ⁻¹ g ⁻¹ CH ₃ OH: 1.37 μmol h ⁻¹ g ⁻¹	[163]
Graphene-g-C ₃ N ₄ (15 wt%)	Daylight bulb, 15 W	CH ₄	CH ₄	5.87 μmol g ⁻¹ (after 9 hour) 2.3-fold than that for g-C ₃ N ₄	[164]
Modified graphene oxide (GO)	300-Watt halogen lamp irradiation	CH ₃ OH	CH ₃ OH	Conversion rate: 0.172 μmol g ⁻¹ h ⁻¹ (Six-fold higher than the pure TiO ₂)	[165]
Cu-Nanoparticle Decorated Graphene Oxide	one-pot microwave process (2 h of visible irradiation)	Cu(NO ₃) ₂ · 3 H ₂ O in ethylene glycol		Conversion rate: 6.84 μmol g-cat ⁻¹ h ⁻¹ (60 times higher than that for pristine GO)	[166]
Platinum modified rGO with TiO ₂ nanotubes	Xenon lamp, 300 W		C ₂ H ₅ OH and CH ₃ COOH	Conversion rate: 1,130 nmol/(h cm ²)	[167]



Graphene derivative TiO ₂	Mercury vapour lamp		Methanol, Ethanol	Ethanol production Rate: 144.7 $\mu\text{mol g}^{-1} \text{h}^{-1}$ at pH 11.0. Methanol production Rate: 47.0 $\mu\text{mol g}^{-1} \text{h}^{-1}$ at pH 4.0.	[168] Article Online DOI: 10.1039/B5MA00750J
Noble metal nanoparticles (Pt, Pd, Ag, Au) immobilized on rGO-TiO ₂	Xenon arc lamp, 500 W (6 h of light irradiation)	CO ₂ and H ₂ O vapor	CH ₄	Conversion rate: 1.70 $\mu\text{mol g}_{\text{cat}}^{-1}$	[169]
Graphene-supported TiO ₂ nanocrystals with coexposed [110] and [115] facets (G/TiO ₂ -001/101)	300 W Xe arc lamp	CO ₂ + H ₂ O	CO	70.8 mmol $\text{g}^{-1} \text{h}^{-1}$ CO yield	[170]
Reduced graphene oxide (rGO)-copper oxide nanocomposites	visible light irradiation	CO ₂	Methanol	Pristine CuO nanorods showed low photocatalytic activity due to fast charge-carrier recombination, producing only 175 $\mu\text{mol g}^{-1}$ methanol. rGO-Cu ₂ O nanocomposites exhibited a fivefold improvement, yielding 862 $\mu\text{mol g}^{-1}$ methanol. rGO-CuO nanocomposites achieved a sevenfold improvement, yielding 1228 $\mu\text{mol g}^{-1}$ methanol.	[171]
GO-supported oxygen-TiO ₂	xenon arc lamp (400 nm)	CO ₂ and H ₂ O vapor	Methane	Methane (CH ₄) yield: 3.450 $\mu\text{mol g}_{\text{cat}}^{-1}$	[172] 2017
CuO/Cu ₂ O nanowire (NW) arrays grafted with reduced graphene oxide (CuO/Cu ₂ O NWAs@rGO)	Xenon arc lamp, 500 W	CO ₂ + H ₂ O	CO	Enhanced CO production compared to bare CuO/Cu ₂ O NWAs due to slower charge recombination and efficient electron transfer through rGO nanosheets Carbon monoxide (0.31 and 0.20 mmol cm ⁻²)	[173]
Pt-sensitized graphene-wrapped defect-induced blue-colored TiO ₂	300 W Xenon lamp	Continuous flow-through CO ₂ + H ₂ O	CH ₄ , C ₂ H ₆	259 $\mu\text{mol g}^{-1}$ CH ₄ , 77 $\mu\text{mol g}^{-1}$ C ₂ H ₆ (7.9% AQY; 5.2% CH ₄ , 2.7% C ₂ H ₆), stable for 42 h	[174]
graphene oxide modified with cobalt metallated aminoporphyrin	450 W Xenon lamp	CO ₂	Formic acid	Formic acid yield: 96.49 μmol in 2 h.	[175]




In ₂ O ₃ -rGO nanocomposites	Visible light	CO ₂ + H ₂ O	CH ₄	953.72 $\mu\text{mol g}^{-1}$	[176]
α -Fe ₂ O ₃ -ZnO rod/reduced graphene oxide (rGO) heterostructure	Visible light & UV-Vis light Xenon Lamp	CO ₂ + H ₂ O	CH ₃ OH	Under visible light: 1.8 $\mu\text{mol g}^{-1} \text{h}^{-1}$, total 5.3 $\mu\text{mol g}^{-1}$ in 3 h; Under UV-Vis: 3.2 $\mu\text{mol g}^{-1} \text{h}^{-1}$, total 9.7 $\mu\text{mol g}^{-1}$ in 3 h; $\sim 10\times$ higher than ZnO; stable (90% activity retained after 3 cycles)	[177]
Poly(3-hexylthiophene) nanoparticles/graphene oxide (P3HT NPs/GO)	Visible light (sunlight)	Gas-phase CO ₂	CH ₃ OH (methanol), CH ₃ CHO (acetaldehyde)	CO ₂ -to-CH ₃ OH production: 3.4$\times$ higher than pristine GO; total solar fuel yield: 5.7$\times$ higher than GO; improved dispersion with SDS nearly 2$\times$ higher yield than without SDS; overall solar-to-fuel conversion efficiency 13.5$\times$ higher than GO	[178]
Chlorophyll-Cu/graphene (Chl-Cu/graphene)	Visible light (420 nm)	CO ₂ + H ₂ O	C ₂ H ₆ (only product)	68.23 $\mu\text{mol m}^{-2} \text{h}^{-1}$ C ₂ H ₆ yield; 1.26% AQE ; high selectivity and stability over 18 h	[179]
Au-TiO ₂ decorated N-doped graphene (ANGT-x, optimized ANGT2)	Xenon lamp, 300 W ($\lambda > 420$ nm)	CO ₂ + H ₂ O vapor	Methane (CH ₄ , highly selective)	Electron consumption rate: 742.39 $\mu\text{mol g}^{-1} \text{h}^{-1}$ (for ANGT2); catalytic activity $\sim 4\times$ higher than ANGT0 and $\sim 60\times$ higher than binary Au-TiO ₂ ; best reported PCO ₂ R rate under comparable conditions	[180]
rGO-grafted NiO-CeO ₂ nanocomposite	Xenon lamp, 300 W	CO ₂ + H ₂ O	Formaldehyde (HCHO)	421.09 $\mu\text{mol g}^{-1} \text{h}^{-1}$ ($\approx 4\times$ higher than pristine CeO ₂)	[181]
G-Ti _{0.91} O ₂ hollow spheres	300 W xenon lamp	CO ₂ and H ₂ O vapor	CO, CH ₄	CO: 8.91 $\mu\text{mol g}^{-1} \text{h}^{-1}$ CH ₄ : 1.14 $\mu\text{mol g}^{-1} \text{h}^{-1}$ $\sim 5\times$ higher total CO ₂ conversion than Ti _{0.91} O ₂ spheres; CO dominant; enhanced charge separation, electron transfer to graphene, and photon-trapping from hollow structure	[182]
Cu _x O/graphene oxide (GO)/Cu-MOF (Cu-BTC) ternary composite photocathode	Xenon lamp 150 W, AM 1.5 filter (100 mW cm ⁻²)	Aq. electrolyte + CO ₂	Ethanol, Methanol and Propanol	Ethanol yield: 162 $\mu\text{M cm}^{-2}$ after 4 h; improved charge separation and CO ₂ binding confirmed by DFT; Cu-BTC composites reported alcohol yields up to 2217 nmol h⁻¹ cm⁻² (MeOH, EtOH, PrOH)	[183]
RGO-CdS nanorods (0.5 wt% RGO)	Visible light, 300 W xenon lamp	CO ₂ and H ₂ O vapor	CH ₄	2.51 mmol h ⁻¹ g ⁻¹ ; $>10\times$ higher than pure CdS; outperforms Pt-CdS under same conditions; RGO acts	[184]

Open Access Article. Published on 13 Hukuri 2025. Downloaded on 2025-11-18 07:30:13.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



				as electron acceptor/transporter, enhancing charge separation and CO ₂ adsorption	View Article Online DOI: 10.1039/D5MA00750J
SWCNT-TiNS (1D-2D) and SEG-TiNS (2D-2D) nanocomposites	UV (365 nm) and visible (>380 nm) light	CO ₂ (water-saturated atmosphere)	CH ₄	Under UV: SEG-TiNS showed up to 3.5× higher CH ₄ production vs TiNS, while SWCNT-TiNS showed 2× improvement. Under visible: SWCNT-TiNS showed up to 5.1× improvement, SEG-TiNS 3.7× , compared to TiNS. SEG-TiNS superior under UV (73.5% more CH ₄ than SWCNT-TiNS), while SWCNT-TiNS superior under visible due to photosensitization.	[185]
Graphene-TiO ₂ (G-TiO ₂ , 2 wt% graphene)	300 W xenon lamp	CO ₂ + H ₂ O vapor system	CH ₄ , C ₂ H ₆	C ₂ H ₆ , 16.8 μmol h ⁻¹ g ⁻¹ ; CH ₄ , 8 μmol h ⁻¹ g ⁻¹ ; Solar fuel production rate is 1.7-fold of TiO ₂	[186]
Ag NW-RGO/CdS NW (ACG-2 wt%)	Visible light, 300 W xenon lamp	H ₂ O (for water-splitting), H ₂ O/CO ₂ (for CO ₂ reduction)	H ₂ , CO, CH ₄ , reduced nitro-aromatic compounds	H ₂ : 70.6 μmol (7× higher than CG-2 wt%); CO: 3.648 μmol g ⁻¹ ; CH ₄ : 1.153 μmol g ⁻¹ ; nitro-aromatic reduction enhanced compared to CG-2 wt%	[187]
Au-Cu/graphene/Cu ₂ O (3D coaxial NW array)	Visible light, 300 W xenon lamp	CO ₂ saturated H ₂ O	CH ₃ OH	18.80 ppm cm ⁻² h ⁻¹ methanol production rate	[188]
Cu ₂ O/RGO	Simulated solar light, 500 W xenon lamp (400 nm)	CO ₂ + H ₂ O	CO, CH ₄	Nearly 6× higher activity than optimized Cu ₂ O and 50× higher than Cu ₂ O/RuOx after 20 h; apparent quantum yield ~0.34% at 400 nm; enhanced photocurrent and stability due to efficient charge separation and RGO protection	[189]
ZnO-RGO	Simulated solar light, 500 W xenon lamp	CO ₂ saturated NaHCO ₃ solution	CH ₃ OH	4.6 μmol h ⁻¹ g ⁻¹ ; 1.7 times higher than pure ZnO	[190]
Fe ₂ V ₄ O ₁₃ /RGO/CdS	Visible light, 300 W xenon lamp	CO ₂ and H ₂ O vapor	CH ₄	2.3 μmol h ⁻¹ g ⁻¹ ; 1.5-fold higher than Fe ₂ V ₄ O ₁₃ -CdS	[191]



Graphene- TiO ₂	Mercury lamp (200 W)	CO ₂ , triethylamine vapor	CO	CO conversion rate: 1.26 μmol mg ⁻¹	[192]
MOF-808/ reduced graphene oxide	Xenon lamp	CO ₂ , H ₂ O	CO	CO conversion rate: 14.35 μmol g ⁻¹	[193]
ZnO/N-doped reduced graphene oxide	Xenon lamp (300 W)	84 mg NaHCO ₃ , 2M H ₂ SO ₄	CH ₃ OH	CH ₃ OH conversion rate: 1.51 μmol h ⁻¹ g ⁻¹ (2.3 and 4.7 times higher than that of the pristine ZnO and commercial ZnO)	[194] 2021
RGO-P25; SEG-P25	UV light: 100 W mercury vapor lamp Visible light: 60 W daylight bulb	CO ₂ and H ₂ O vapor	CH ₄	Under UV light: - 1.9 μmol m ⁻² h ⁻¹ , comparable to TiO ₂ - 8.5 μmol m ⁻² h ⁻¹ , 4.5 times higher than TiO ₂ Under visible light: - 1.3 μmol m ⁻² h ⁻¹ , 2.3 times higher than TiO ₂ - 4.0 μmol m ⁻² h ⁻¹ , 7.2 times higher than TiO ₂	[195]

5. Mechanistic insight and charge dynamics in graphene based photocatalytic CO₂ Reduction

Rational design of graphene-based materials with enhanced photocatalytic properties necessitates some understanding of the mechanisms governing photocatalytic CO₂ reduction. The addition of graphene and its derivatives can significantly alter band structures, light harvesting efficiencies, and charge carrier dynamic behaviours[196]. In this section, we will also discuss the nature of interfaces that separate and transport charge in conjunction with graphene's contributions to improve the performance of photocatalysts, as well as the theoretical and experimental frameworks that support these operational mechanisms[197].

5.1 Charge separation and migration at graphene interfaces

The effective production, separation, and transportation of photo-induced electron-hole pairs are key to photocatalytic efficiency. Rapid recombination of these carriers due to charge carrier motion limits the number of electrons available for reducing CO₂ on typical semiconductor photocatalysts[198]. The unique structure of graphene acts as both a mediator and an electron acceptor at the interface to eliminate this challenge[199]. Photogenerated electrons from the CB are transferred to the graphene



sheet because of the energy level alignment and difference in the two Fermi levels when semiconductors like TiO_2 , ZnO , or $\text{g-C}_3\text{N}_4$ are combined with graphene, or rGO[200]. Transfer of these electrons decreased their chance to recombine and increases their time to interact with the adsorbed CO_2 on the surface as shown in (Fig.17) [201, 202].

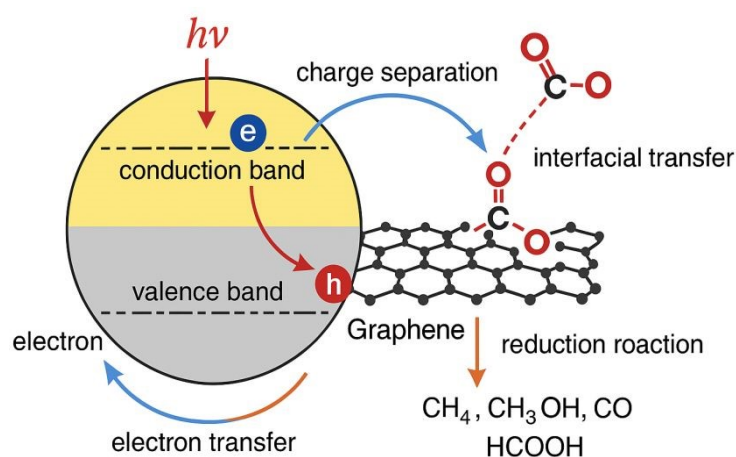


Fig.17 Mechanistic insights in charge transfer dynamics. Reprinted with the [203], copyright@2025, RSC.

Moreover, the two-dimensional structure and high conductivity ($\sim 10^4$ S/cm) of graphene provide a rapid and directional pathway for charge migration[204]. This network of conductive sheets reduces the distance between separate photocatalytic nanoparticles and therefore facilitates a more uniform distribution of charge carriers across the surface of the catalyst, and greater electron migration between adjacent particles[205].

5.2 Synergistic roles of graphene in light absorption and carrier mobility

Even without a bandgap, pristine graphene lacks the characteristics of an intrinsic photoactive substance; nonetheless, when combined with other materials it can improve light harvesting and charge transportation capabilities in photocatalysts[206]. By limiting nanoparticle agglomeration in the composite and ultimately increasing light scattering centers throughout the composite material, graphene enhances the light absorption via improved light harvesting[207]



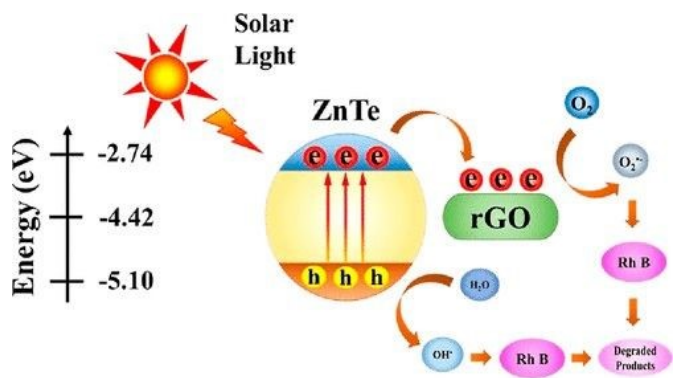



Fig.18 Plausible Mechanism of the Photocatalytic Degradation Process of RhB Containing the R-ZT Catalyst under Solar Light Irradiation, Reprinted with the Ref [208], copyright@2022, ACS.

In addition, when graphene is mixed with plasmonic metals like Au or Ag, it will modify the optical response of the composite system[209]. The localized surface plasmon resonance (LSPR) of noble metal-graphene hybrids will lead to an enhancement in visible light absorption and induce hot electrons that may be transported to graphene and used in CO₂ reduction as shown in (Fig.18) [210]. Graphene also significantly enhances the mobility of charge carriers. Due in large part to the delocalized π -electron system, the energy wasted when carriers migrate is minimized since it offers a fast transport path. Graphene can act as reasonably inert, solid-state electron mediators in Z-scheme photocatalytic setups, recombining less energetic electrons and holes from the two different semiconductors in a selective manner, while still retaining the high redox potential of the remaining charge carriers[13, 211, 212]

5.3 Experimental and theoretical investigation

A large body experimental and theoretical evidence supports the application of graphene modifications to photocatalytic reactions [213]. Charge dynamics in graphene-based photocatalysts have been assessed by the use of methods such as surface photovoltaic (SPV) measurements, electrochemistry and impedance spectroscopy (EIS) measurements, photoluminescence (PL) spectroscopy, and time-resolved fluorescence[214-216].



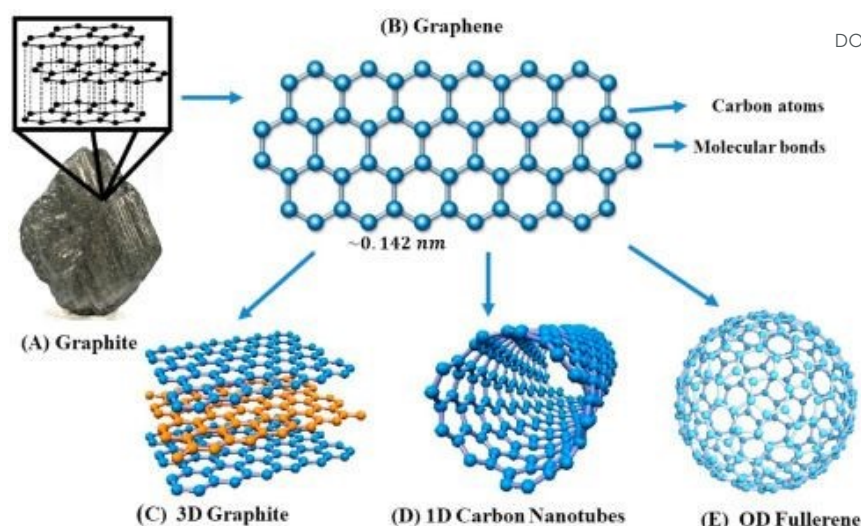

View Article Online
DOI: 10.1039/D5MA00750J

Fig.19 The Schematic illustration of the Origin and the transformation of graphite to graphene's atomic structure. The transformation process shows that graphene, a 2D basic unit of carbon can be folded into (C) 3-D Graphite (D) rolled into 1-D Nanotubes (E) and folded into 0-D Fullerene, Reprinted with the Ref [217], copyright@2023, ACS.

For examples shown in (Fig.19), hybrids containing graphene often showed reduced emission intensity in PL spectra, which indicates reduced electron-hole recombination[218]. The increased interfacial conductivity was demonstrated by EIS measurements, which generally show reduced charge-transfer resistance for graphene-based composites as compared to clean semiconductors[219, 220]. Transient absorption spectroscopy (TAS) and time-correlated single photon counting (TCSPC) offer direct insight of charge carrier lifetimes, with graphene-based materials with much increased lifetimes - often by orders of magnitude[221, 222]. Surface photovoltage imaging experiments showcase better charge separation and charge carrier dispersion on graphene-modified surfaces[223].

Modelling approaches utilizing DFT have assisted in elucidating interfacial charge transfer, modification of the band structure, and CO₂ adsorption energies[224]. DFT simulations suggest charge transfer to heteroatom-doped graphene (for example N-doped, B-doped) exhibits higher CO₂ binding energy and far lower energy barriers for multi-electron transfer processes[225]. Coupling with graphene may better align semiconductor conduction or valence band edge with CO₂ reduction redox potentials, as simulations have indicated[226, 227].




5.4 Graphene induced defect engineering and bandgap modulation

Defects can markedly alter the electrical properties and reactivity of graphene for both intrinsic defects and defects created during synthesis[228]. Specifically, functional groups, vacancies, Stone-Wales defects and dopants allow for effective sites for CO₂ adsorption and activation, due to their capacity to modify the band structure and introduce localized electronic states[229, 230]. Defect engineering in GO or rGO opens up possibilities for bandgap tuning and reactive oxygen-bearing functionalities (such as -OH, -COOH, -C=O) that not only act as anchoring sites for the nanoparticles, also allows for dipole and hydrogen bonding with CO₂ molecules to enhance contact of CO₂ with the reaction sites[231, 232]. These defects can also be potential charge trapping sites to stabilize catalytic intermediates and extend charge separation steps[233].

Heteroatom doping with N, S, B, or P can change the electronic density and bandgap of graphene to improve photocatalytic activity further. For example, N-doped graphene establishes electron-rich regions which can facilitate proton-coupled electron transfer and activation of CO₂ because of the lone pairs which donate electrons to nearby carbon atom(s)[195, 234]. Engineering the band structure of graphene in a heterojunction is also possible with 2D/2D heterojunctions. Heterojunctions with layered materials such as MoS₂ or g-C₃N₄ provide strong interfacial interaction with few 2D materials while spatially separating electrons and holes through the band alignments result in staggered band alignments (type-II or Z-scheme)[235, 236].

Oxygen-doped graphene (GO and rGO) plays a particularly important role due to the abundance of oxygen-containing functional groups, which not only improve the dispersibility of graphene but also provide abundant active sites for anchoring semiconductor species[237]. Residual oxygen groups in rGO are reported to enhance electron transfer by serving as electron-accepting and shuttling sites, while also inducing bandgap narrowing in semiconductor composites through chemical bonding (e.g., Ti-O-C linkages) as shown in (Fig.20) [238]. This leads to red-shifts in light absorption and enhanced photocatalytic performance. However, oxygen



functionalities also introduce a trade-off: while they increase absorptivity and porosity, they may reduce carrier mobility by disrupting the π -network. Interestingly, graphene oxide can also act as a standalone semiconductor with a tunable bandgap, although its photoactivity is limited by instability under prolonged irradiation.

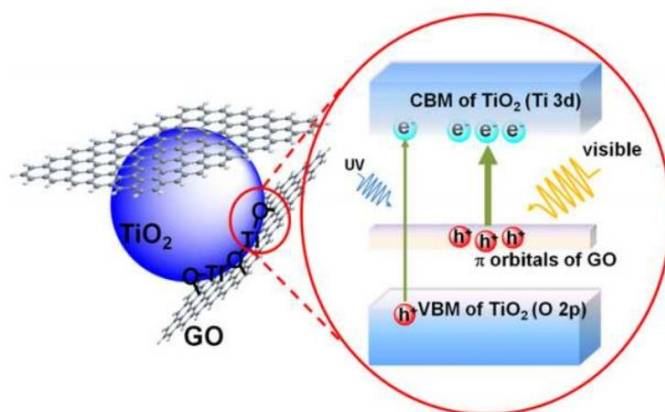



Fig. 20 Schematic representation of Ti-o-c chemical bonding which introduce a localized state and render band gap narrowing, Reprinted with the Ref[239] copyright@2019, Springer.

Nitrogen-doped graphene (NGR) has attracted significant attention as a superior alternative to rGO due to its ability to preserve more of the sp^2 carbon network while introducing active nitrogen sites[240]. Nitrogen atoms contribute additional π -electrons, thereby improving the electronic density of states near the Fermi level and markedly enhancing conductivity compared to rGO as shown in (Fig.21) [241]. This increased conductivity promotes efficient electron-hole separation, delays recombination, and boosts photocatalytic durability. Furthermore, different nitrogen configurations – graphitic, pyridinic, and pyrrolic – introduce distinct surface states that act as catalytic centres and improve interfacial contact with semiconductor nanoparticles, thereby strengthening photocatalyst-support interactions.



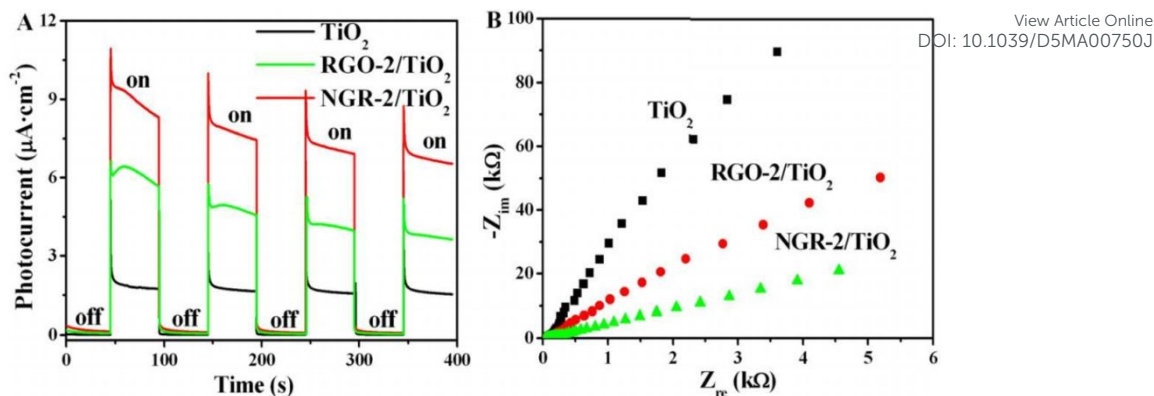


Fig 21. Left: the transient photocurrent of TiO_2 , RGO/TiO_2 and NGR/TiO_2 to a chopped light irradiation. Right: Nyquist plot of electrochemical impedance spectra for TiO_2 , RGO/TiO_2 and NGR/TiO_2 . Reprinted with the Ref[242], copyright@2025, Elsevier.

Phosphorus-doped graphene (P-G) has also shown promise, as P atoms induce semiconducting behaviour in graphene and open a tunable bandgap (up to ~ 2.85 eV), enabling visible-light-driven photocatalysis[243]. The incorporation of P atoms reduces defect density while simultaneously enhancing the material's electronic properties. In particular, P-doping Favors hydrogen evolution reactions under visible light, outperforming GO and rGO analogues in photocatalytic hydrogen generation[244].

Sulfur doping, particularly in nitrogen-sulfur co-doped graphene quantum dots (N, S-GQDs), further extends visible-light absorption due to new surface states introduced by sulfur functionalities ($\text{C}=\text{S}$, $\text{S}=\text{O}$)[245]. These dopants enable broad absorption bands in the visible region and confer sensitizing properties, allowing GQDs to act as efficient electron donors when coupled with semiconductor photocatalysts like TiO_2 [246]. The enhanced photoluminescence and surface charge properties imparted by sulfur doping strengthen the structure-activity relationship in such composites.

Taken together, these heteroatom modifications significantly broaden the photocatalytic capabilities of graphene-based materials. Oxygen doping primarily facilitates surface reactivity and bandgap modulation, nitrogen doping enhances conductivity and electron mobility, phosphorus doping introduces stable bandgap engineering with reduced defect states, and sulfur doping expands visible-light utilization. The synergy of these dopants not only improves charge separation and

transport but also enables selective production of solar fuels and chemicals under tailored reaction conditions.


6. Influence of synthesis strategies on photocatalytic efficiency

The structural attributes of graphene-based photocatalysts chiefly determined through the synthesis approaches of the working moieties - are directly related to their performance in CO₂ reduction[247]. The various approaches will affect the shape, defect density of the material, crystallinity, surface chemical properties and interfacial contact between the graphene component and the active components of the composite all impact the catalytic efficiency, charge separation and light absorption[248]. This section will raise discussion about the impact that various synthesis approaches have on the photocatalytic activity and sustainability of graphene-based materials, focusing on hydrothermal, electrochemical, photoreduction and green synthesis processes.

6.1 Hydrothermal / Solvothermal approach

Graphene-based nanocomposites are frequently developed by hydrothermal and solvothermal methods, which are also economic and scalable methods with the possibility of producing well-crystallized forms that may have good interfacial contact between graphene and active components[249]. During the hydrothermal/solvothermal method shown in (Fig.22), GO or rGO is readily dispersed with metal precursors in aqueous or organic solutions before heating and pressurizing a sealed autoclave[250]. Over these heating and pressurizing conditions, nucleation and growth of semiconductor or metal oxide nanoparticles (e.g., TiO₂, ZnO, BiVO₄) can occur directly on the peeled-off GO or rGO sheets. Greater interfacial coupling is also known to improve photocatalytic CO₂ reduction via better electron transfer and suppressing electron-hole recombination.

Fine tunings of synthesis conditions have the potential to induce vast differences in the catalytic activity of hydrothermally synthesized materials. A good example is how different reaction temperatures alter the crystallinity of the precipitated nanoparticles. Elevated temperatures often help promote the crystallinity or order of solid, thus minimizing structural defects that act as recombination sites for charge carriers, whilst also increasing the lifetime of charge carriers. This outcome was associated with ZnO-



graphene hybrids, where increased CO₂ to CO conversion efficiencies and crystallinity resulted from elevating the hydrothermal temperature from 120 °C to 180 °C, and several crystallinity defects resulting in reduced conversion efficiencies. Conversely, if the temperature is too high charge carriers can act as glues between nanoparticles resulting in agglomeration which reduces both the surface area and number of active sites in a sample which can subsequently decrease CO₂ adsorption ability. Time is also critical; longer hydrothermal times frequently enhance stability and increase the relative size and homogeneity of nanoparticles, whilst promoting better interactions in the hybrid structure of nanoparticles-graphene. However, prolonged growth also reduces defect density which may limit the availability of catalytically active sites. In contrast, shorter reaction times can generate smaller nanoparticles with higher defect density, potentially increasing catalytic activity by creating additional active centers, albeit at the expense of structural stability.

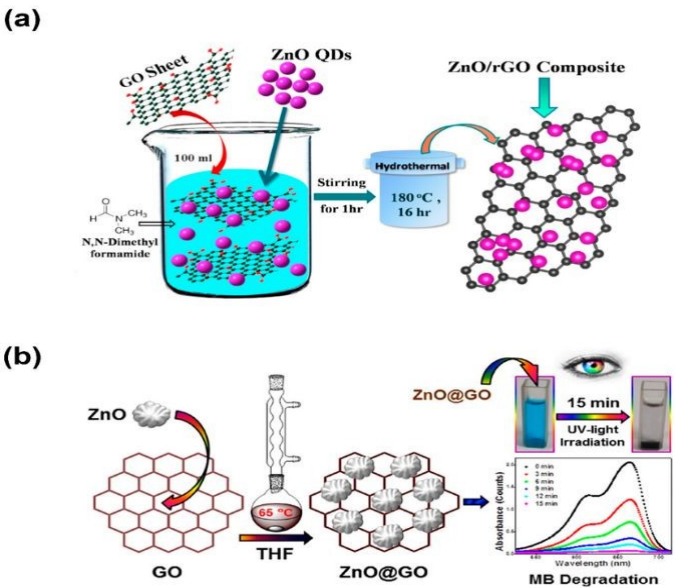


Fig.22 Illustration of the (a) hydrothermal Reprinted with the Ref [251] copyright@2016, Elsevier and (b) solvothermal synthesis of ZnO/GO nanocomposites, Reprinted with the Ref [252], copyright@2024, MDPI.


The pH of the precursor solution and the concentration of metal salts are just as important as temperature and time for nucleation and growth of the nanoparticles. On graphene, we typically produced smaller, more evenly dispersed nanoparticles from faster nucleation rates at higher pH. This is important for the effective electron

transport of the composite. The precursor concentration affects loading density of the nanoparticles: mid-range concentrations evenly distribute the loaded nanoparticles and help maintain graphene conductivity and improve electron-hole separation, while extreme concentrations can lead to nanoparticle collisions with one another, blocking graphene surfaces and limiting charge mobility. The ultimate impact on photocatalytic activity, photon absorption and CO₂ reduction rate is dependent on the balance of factors of crystallinity, defect density, surface chemistry and interfacial contact - all determined collectively from a balance of these interdependent factors[253].

6.2 Electrochemical and photoreduction method

For producing graphene-based photocatalysts both electrochemical and photoreduction technologies have become attractive alternatives to conventional chemical reduction. As they can be applied in relatively mild conditions, and because they offer precise control of both the level of reduction and nanoparticle deposition, both methods are considered to be "greener" since they do not use harsh reducing chemicals. For these reasons, they are suitable for making composites with electrical and structural properties which can be tuned to directly affect their efficiency for photocatalytic CO₂ reduction.

Electrochemical Reduction, involves the application of an electrical bias to GO films or dispersions in an electrolyte medium, removing oxygen functional groups while partially reforming sp²-hybridized carbon networks[254]. Extent of reduction is directly linked to applied potential, reduction time, and electrolyte composition[255]. GO deoxygenation accelerates with applied voltage; the higher the applied voltage, the greater the extent of deoxygenation, increasing electrical conductivity and enabling rapid electron transfer across rGO films. However, excessive reduction may strip too many oxygenated groups from the rGO, leading to a decrease in surface polarity and the number of CO₂ adsorption sites, marking a negative effect on catalytic selectivity. Reduction duration is equally important in rGO production: short reduction times yield partially rGOs with a predominance of oxygen functionalities that subsequently act as anchoring sites for metal nanoparticles, while long reduction times increase conductivity, but decrease oxidation and thus limit surface



906 reactivity.[256] As ionic strength and metal cation presence can regulate nanoparticle
907 nucleation and dispersion, the electrolyte's composition can also influence this
908 process. When noble metals (Ag, Au, and Pt) or TiO₂ are deposited on rGO substrates
909 by electrochemical reduction, for example, there is a close interfacial contact, which
910 aids in effective electron transmission and better charge separation at the graphene-
911 semiconductor interface.

912 On the other hand, photoreduction is a process that makes use of light irradiation
913 (typically UV or visible light) along with appropriate sacrificial agents (for example,
914 ethanol, methanol, or other organic donors) to reduce GO, or reduce metal ions to
915 graphene sheets in parallel to reducing GO. This is advantageous because it delivered
916 a nanohybrid where there was a clean surface free from any (chemical) residual, unlike
917 traditional chemical reduction routes. The parameters of photoreduction that
918 influence it include: (1) the wavelength of light, and the intensity of light; (2) the time
919 of illumination using the light; and (3) the concentration of sacrificial agent present.
920 Short wavelength UV light, gives high energy photons that can drive highly
921 efficacious GO reduction, and rapid nanoparticle nucleation; while visible-light-
922 assisted photoreduction, is greener and more amenable to scale up. Long illumination
923 times will likely enhance the level of reduction, and nanoparticle loading; however,
924 excessive illumination can result in particle overgrowth or photothermal
925 agglomeration. Additionally, sacrificial agent concentration also plays a role:
926 moderate concentrations will facilitate the efficient transfer of photogenically
927 generated electrons to GO or metal precursors, and high concentrations will result in
928 either incomplete reductions or residual by-products that may passivate catalytic
929 sites.

930 Electrochemical and photoreduction techniques are most effective when creating
931 nanohybrids with uniformly dispersed nanoparticles good interfacial contact and
932 tunable surface chemistry. These characteristics promote charge transfer efficiency,
933 increase carrier lifetimes, and provide large active surface sites for the adsorption and
934 activation of CO₂, all of which in turn have a direct influence on the catalytic
935 efficiency. Additionally, these techniques produce low energy and less toxic by-
936 products while allowing for nominally room- to low-temperature reactions, benefiting




sustainability goals for the scalable production of graphene-based photocatalysts[257].

6.3 Green synthesis and sustainability concern

Due to growing emphasis on green chemistry, green synthesis protocols for graphene-based photocatalysts have gained significant attention[258]. With regard to conventional protocols that occasionally employ toxic solvents, high redox agents or high energy requirements, green protocols involve non-toxic solvents, biological redox agents or energy-saving protocols such as microwave-assisted or mechanochemical syntheses. The new technologies both minimize environmental effects and offer new surface functionalities that enhance photocatalytic CO₂ reduction[259].

One of the most frequently adopted green methods is biogenic and plant-extract-mediated reduction. Plant-derived, fungus-derived, or bacterial extracts comprise polyphenols, flavonoids, alkaloids and sugars that serve both as reducing and stabilizing agents while converting GO to rGO and depositing metal nanoparticles. The composition of the extracts directly affects catalytic properties. Polyphenol-laden extracts improve the incorporation of the surface graphene's oxygenated functional groups, increasing hydrophilicity and CO₂ adsorption ability. Flavonoids and proteins however, may act as a capping agent and decrease nanoparticle size and improve dispersion[260].

Microwave-assisted synthesis is another sustainable approach, where precursors are fairly uniformly heated quickly, and the time of reaction and energy consumption is reduced significantly versus traditional hydrothermal processing. The microwave power and exposure time will greatly determine the end material properties. In general, higher microwave power leads to better crystallinity and interfacial coupling, by promoting a faster reduction of GO and nucleation of metal/semiconductor nanoparticles. Extreme microwave power or excessive irradiation times can cause uncontrolled growth or agglomeration of nanoparticles, decrease the active surface area and affect mass transfer. With that stated, optimal microwave parameter manipulation allows the creation of highly porous nanocomposites with controlled shapes, large surface areas and enhanced light absorption efficiency.





Mechanochemical (solvent-free) synthesis is another environmentally-friendly method that does not require an organic solvent. In the mechanochemical process, graphene sheets and catalyst precursors are closely combined by mechanical forces, including ball milling. The choices in milling speed, duration of milling, and ball-to-powder mixing ratio will directly affect the surface roughness, defects, and anchoring of nanoparticles on graphene. For example, in terms of CO₂ adsorption or electron-hole separation, short or low energy-modified milling may create mild defects, allowing for better homogenous dispersion of catalyst in the graphene encapsulated sample. In contrast, large defects created by long milling time (or high energy) can serve as charge recombination sites, reducing the overall catalytic activity of the catalyst. Therefore, optimization is required in order to properly assess the trade-off between the disadvantage of deterioration of structural integrity, and the opportunity to engineer better defects from persistent mill.

Taken collectively, green synthesis methods offer benefits that are considerable in terms of scalability and sustainability and options for tuning the electrical and structural properties of graphene-based photocatalysts as shown in (Fig.23). Often, they lead to composites with lower crystallinity and more heterogeneity compared to conventional hydrothermal or chemical methods, which can detract from long-term stability and reproducibility. Therefore, future studies should focus on optimizing these methods for green chemistry and catalysis, perhaps allowing controlled parameter tuning and hybridization, such as biogenic reduction followed by microwave irradiation[261].

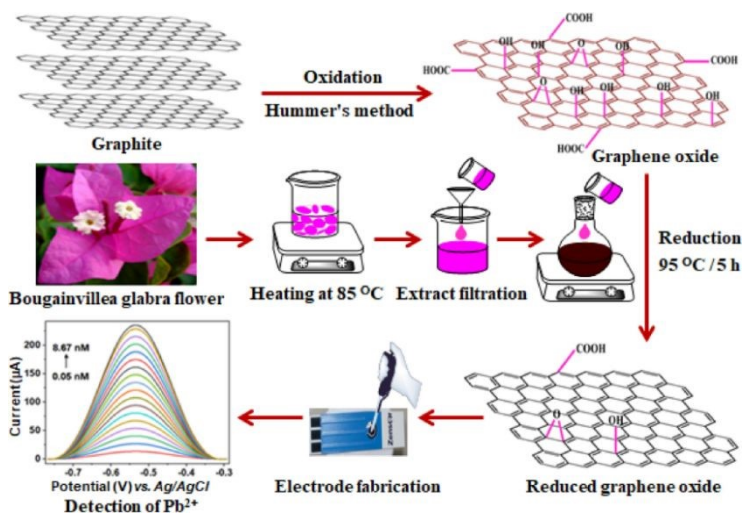



Fig.23 Green preparation method of rGO, Reprinted with the Ref [262], copyright@2025, Springer View Article Online
DOI: 10.1039/D5MA00750J

6.4 Morphological tuning and surface area control

The catalytic efficiency of graphene-based photocatalysts is typically determined by controlling morphology and surface design rather than the selection of the synthesis method[263]. The morphological parameters of the composite material which contribute to photocatalytic efficiency through their influence on light absorption, charge separation, kinetics of surface reaction and CO₂ adsorption are equally as important as the innate electrical properties of the material[264]. Therefore, it is progressively more common to use rational modification of morphology when seeking to optimize catalytic efficiencies.

The finest strategy to produce a 3D graphene material is to produce it in the form of hydrogels, foams or aerogels. These are composite structures usually produced via hydrothermal self-assembly or freeze-drying, yielding connected porous networks comprising extremely high porosity and large surface areas[265]. Not only does increased porosity increase light exposure into the catalyst matrix and mass transfer of the CO₂ molecules to/from the active site, but increased porosity also increases active sites due to the increased surface area. For example, size distribution of pores will be affected by the rate at which it is frozen. Rapid freezing yields small closed holes with potential accessibility issues, while slow freeze-drying creates larger interconnecting pores, which can be beneficial for gas diffusion. Thus, this parameter can directly affect the kinetics of CO₂ adsorption and reduction.

The size and spatial distribution of nanoparticles on graphene supports are important factors. During synthesis, the kinetics of nucleation, the use of surfactants or templates, and the concentration of precursors can be varied and achieve morphological control. Smaller and more uniformly dispersed particles form more catalytically active sites and smaller distance of electron transport channel. However, overcrowding of particles from excessive nucleation can reduce graphene's conductivity and disrupt charge mobility. On the other hand, larger nanoparticles can decrease the density of surface-active sites while promoting crystallinity. Producing a suitable morphology will require controlling the syntheses conditions in such a way



to find a suitable balance between exposure of active surface sites and the efficiency of charge separation.

Morphological modification also depends upon defect engineering. Localized states that act as charge-trapping or catalytic sites are added to graphene's band structure when structural defects such as vacancies, edge sites and even heteroatom dopants (N, S, and B) are embedded (i.e., with an atomic localization)[266]. Because defects modified during the synthesis improve CO₂ adsorption via more significant binding interactions with intermediates such as CO₂⁻ as formed and adsorbed at these sites, defects also help morphology-based modification. Defects must be controlled since stability might be compromised and non-radiative recombination could be enhanced if defect densities are too high. For example, nitrogen-doped graphene aerogels can exhibit increased selectivity to the production of CO by stabilizing COOH intermediates, but too much nitrogen-doping can lead to distortion of the carbon lattice structure which can reduce conductivity.

Finally, hierarchical and mesoporous structures enhance photocatalytic performance by combining mesopores (to provide a greater active surface area) and macropores (for mass transfer). Template-assisted synthesis allows precise control on pore size and connectivity. Surfactant/template to precursor ratio is important; if too little surfactant is used the porous structure may partially collapse, while more surfactant loading typically adds to the pore volume and surface area. The use of morphological control mechanisms provides the following synergistic balance of surface area, mass transport and charge transfer dynamics.

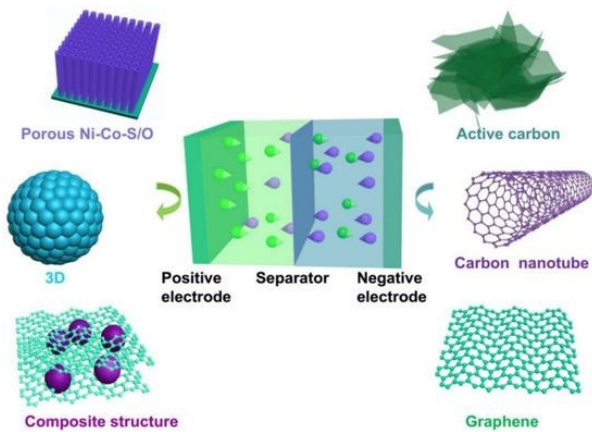


Fig. 24 Taking Advantage of Graphene's Surface Area for Advanced Applications, Reprinted with the Ref [267], copyright@2025, MDPI.

Surface engineering and morphological tuning are successful strategies for increasing photocatalytic CO₂ reduction capability in graphene-based composites as shown in (Fig.24)[268]. From careful manipulation of physical features (i.e., pore shape, nanoparticle size and dispersion, and defect density) it is possible to optimize light harvesting, facilitate charge separation, and uncover a large number of catalytic sites. The strategies we have proposed help bridge the gap between material development and functional performance.

Table 4: Summary of Synthesis Methods and Their Impact on Catalytic Properties

SN	Synthesis Method	Key Parameter	Effect on Material Properties	Impact on CO ₂ Photocatalysis	Ref.
1	Hydrothermal/ Solvothermal	Temperature	Higher crystallinity at elevated temperature; excessive heating causes nanoparticle aggregation and surface area loss	Improves charge carrier lifetime; excessive temperature reduces CO ₂ adsorption	[269]
2	Hydrothermal/ Solvothermal	Reaction Time	Longer times → larger particles, lower defect density; shorter times → smaller particles, higher defect density	Balances stability and catalytic site density	[270]
3	Hydrothermal/ Solvothermal	pH / Precursor Concentration	Controls nucleation density and nanoparticle dispersion on graphene	Enhances interfacial contact and electron transfer	[271]
4	Electrochemical Reduction	Applied Potential	Higher voltage improves conductivity but may reduce surface oxygen groups	Improves electron mobility but may lower CO ₂ binding	[272]
5	Electrochemical Reduction	Electrolyte Composition	Ionic strength and cations influence nanoparticle deposition density and distribution	Better nanoparticle anchoring, enhanced interfacial charge separation	[273]
6	Photoreduction	Light Wavelength & Intensity	UV enables fast GO reduction; visible-light more sustainable but slower	Generates clean-surface composites with high electron transfer	[274]
7	Photoreduction	Sacrificial Agent Concentration	Moderate levels promote efficient reduction; excess may leave residues and passivate sites	Affects nanoparticle loading and catalytic efficiency	[275]



8	Green Synthesis (Biogenic)	Extract Composition	Polyphenols, flavonoids add functional groups enhancing CO ₂ adsorption and selectivity	Improves selectivity and CO ₂ affinity; variability limits reproducibility	[276]
9	Green Synthesis (Microwave-assisted)	Microwave Power & Duration	Rapid, uniform heating improves crystallinity; excessive power causes agglomeration	Reduces reaction time and energy input; optimized power enhances porosity and activity	[277]
10	Green Synthesis (Mechanochemical)	Milling Speed / Time	Creates defects and dispersion; excessive milling may cause too many recombination centres	Enhances CO ₂ adsorption via defects; excessive defects cause recombination losses	[278]
11	Morphological Tuning	Freeze-drying Rate	Slow rate → larger pores, better diffusion; fast rate → smaller, closed pores	Enhances mass transport and light penetration	[279]
12	Morphological Tuning	Surfactant / Template Ratio	Controls mesopore volume, active surface exposure	Increases active surface area and catalytic site exposure	[280]
13	Defect Engineering	Dopant Concentration	Introduces localized charge-trapping sites; excess doping distorts lattice, lowers conductivity	Stabilizes intermediates and boosts selectivity; excess defects hinder performance	[281]

7. Photocatalytic Performance Evaluation

7.1 Experimental Conditions and Reactor Configurations

The evaluation of photocatalytic performance requires standardized and reproducible experimental setups. The three main reactor configurations employed are slurry reactors, flat-panel reactors, and microreactors each providing distinct benefits for light distribution and reactant flow. To ensure comparability, parameters such as light intensity (W/m²), irradiation wavelength, CO₂ pressure and flow rate and reaction temperature must be carefully controlled.[282] For instance, slurry reactors with simulated solar light (AM 1.5G, 100 mW/cm²) have been widely used, while microreactors allow higher precision with CO₂ pressures up to 2 bar and light intensities ranging from 50–150 mW/cm². The use of monochromatic LEDs (420–650 nm) in some studies enables direct correlation between catalyst absorption



and activity, providing more detailed insights into charge transfer mechanisms.

7.2 Effect of CO₂ Pressure, Light Source, and Co-Catalysts

Photocatalytic activity exhibits high sensitivity to external operating conditions. Increasing CO₂ pressure enhances reactant solubility and adsorption, leading to higher yields[283]. For example, graphene-TiO₂ composites achieved a CO production rate of 120 $\mu\text{mol g}^{-1} \text{h}^{-1}$ at 1 atm CO₂, which increased to 210 $\mu\text{mol g}^{-1} \text{h}^{-1}$ when the pressure was raised to 3 atm. Similarly, the choice of light source strongly influences activity: visible light irradiation ($\lambda > 420 \text{ nm}$, 300 mW/cm²) resulted in a 2.3-fold higher CH₄ yield for N-doped graphene/g-C₃N₄ compared to UV-only excitation. The addition of co-catalysts such as Pt, Cu, or Ni facilitates electron trapping and catalytic site formation. For instance, Pt-decorated graphene-ZnO composites exhibited an AQE of 6.2% under 365 nm irradiation, significantly higher than the bare composite (2.8%).

7.3 Performance Metrics its Yield, Selectivity and Quantum Efficiency

The primary performance indicators for CO₂ photoreduction include product yield ($\mu\text{mol g}^{-1} \text{h}^{-1}$), product selectivity (%), apparent quantum efficiency (AQE), and solar-to-fuel efficiency (STF)[284]. Recent reports demonstrate that graphene-based hybrids significantly outperform conventional photocatalysts[258]. For example, graphene-Cu₂O systems achieved a CO yield of 320 $\mu\text{mol g}^{-1} \text{h}^{-1}$ with 82% selectivity under AM 1.5G illumination (100 mW/cm²), while TiO₂ under identical conditions produced only 75 $\mu\text{mol g}^{-1} \text{h}^{-1}$ with 45% selectivity. Similarly, graphene/g-C₃N₄ composites delivered CH₄ yields of 210 $\mu\text{mol g}^{-1} \text{h}^{-1}$ with AQE values of 5–8%, whereas pristine g-C₃N₄ typically showed <2% AQE. Reaction profiles are routinely characterized via gas chromatography (GC) for gaseous products and high-performance liquid chromatography (HPLC) for liquid intermediates.

7.4 Benchmarking with Conventional and Other Advanced Photocatalysts



Systematic benchmarking against conventional and advanced photocatalysts provides quantitative insight into the role of graphene[285]. For instance, under identical AM 1.5G conditions, graphene-perovskite composites achieved CO₂ conversion rates of 410 μmol g⁻¹ h⁻¹ with 85% CO selectivity and stability exceeding 120 h, compared to bare perovskites which exhibited only 160 μmol g⁻¹ h⁻¹ with 62% selectivity. Likewise, graphene-modified ZnO maintained stable activity over 100 h, while pure ZnO lost 40% of its activity within 30 h. Statistical analysis and recent studies reveals consistent trends: (i) graphene incorporation enhances quantum efficiencies from 1–3% to 5–12%; (ii) CO₂ conversion rates increase 2–5 fold relative to pristine semiconductors; and (iii) selectivity toward CO and CH₄ improves by 20–40%. These results underscore the importance of graphene as an electron mediator and structural stabilizer, establishing reliable structure–activity relationships for future catalyst design as shown in (Fig.25).

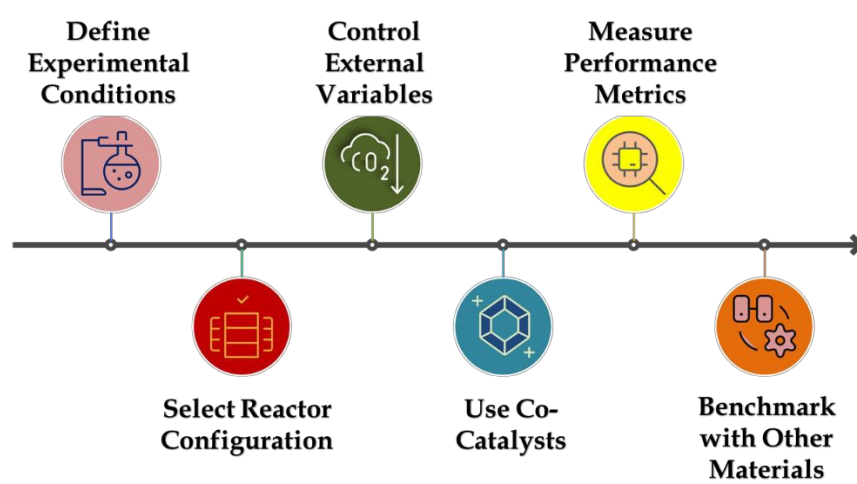


Figure: 25 Experimental setup and performance evaluation of graphene

8. Challenges and Limitations

8.1 Stability and Recyclability of Graphene-Based Catalysts

Extended use of graphene based photocatalysts often causes oxidation, mechanical delamination or photodegradation. Examination of recyclability calls for stability tests involving several photocatalytic cycles and extended illumination. Protective coverings or core-shell construction could help to reduce degradation issues.

8.2 Scale-Up and Cost-Effectiveness

The commercial deployment of these materials faces challenges because of large-scale synthesis difficulties and uniformity problems and high production costs despite positive lab-scale results. The development of continuous hydrothermal synthesis and roll-to-roll graphene film production techniques represents current research directions for scalability[286]. The evaluation of economic viability requires a balance between material costs and energy consumption and catalyst durability.

8.3 Standardization of Testing Protocols

The current differences in testing methods produce results that are both inconsistent and non-comparable between different research groups. International consortia and standard-setting organizations are promoting uniform approaches which include catalyst pre-treatment and analytical instrument calibration and error reporting.

8.4 Toxicity and Environmental Impact of Nanomaterials

Graphene-based nanomaterials (GBN) have been developed with the purpose of photo catalytically reducing CO₂ emissions, meaning GBNs could have a large positive impact on the environment, however, their potential health and environmental risks must be considered. Several studies have reported that GO and rGO cause mammalian cells oxidative stress, membrane damage and inflammation depending on their surface chemistry, size, and dose. In aquatic ecosystems, GBNs have been shown to interact with microorganisms, algae, and fish in ways that impact growth, reproduction, and metabolism, which raises ecotoxicological concern. Chronic exposure to GO has been linked to diminished algal primary productivity and with accumulated discharge of GO in higher trophic levels. And with GBN persistence in soil and water running the risk of unknown cumulative effects, pathways for degradation such as photodegradation, microbial breakdown, and oxidative transformation are only understood in part. [287].

In response to these concerns, regulatory groups have started to take action. The European Chemicals Agency (ECHA) and the U.S. Environmental Protection Agency (EPA) have stressed that nanomaterial safety evaluations and life-cycle assessments of graphene-based materials should be nano specific. However, the regulatory environment is still evolving, and very few regulations established have standardized protocols for toxicity testing, disposal, and risk assessment. Hence, when considering



the safety of graphene nanomaterials in photocatalytic technologies, future studies must prioritize systematic research on environmental fate and bioaccumulation potential, as well as implementation of safe-by-design practices as shown in (Fig.26).

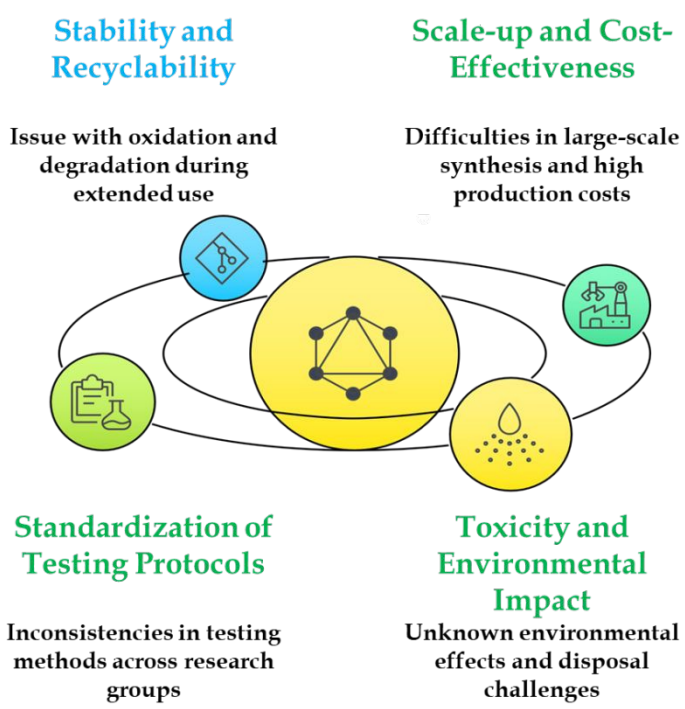


Fig. 26 Overcoming challenges in graphene-based catalysts for CO₂ reduction.

Open Access Article. Published on 13 Hukuri 2025. Downloaded on 2025-11-18 07:30:13.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

9. Recent Advances and Emerging Trends

9.1 Machine Learning and AI in Photocatalyst Design

Machine learning (ML) algorithms, such as random forests and neural networks, are being trained on databases of photocatalytic performance to predict new material combinations with high efficiency. These tools accelerate discovery cycles and reduce experimental workload by identifying key descriptors for performance.

9.2 Single-Atom Catalysts and Defect Engineering (SACs)

SACs doped into the lattice of graphene or anchored on it provide customized electronic environments and optimized atomic efficiency[288]. Especially for multi-electron reduction pathways, these active sites exhibit high turnover frequencies (TOFs) and selectivity. By improving reactivity and establishing anchoring sites, defect engineering enhances SACs.

9.3 Hybrid Systems: Graphene with MOFs, COFs, and Perovskites

The combination of graphene with MOFs, COFs and perovskites produces hybrid systems that unite graphene stability and conductivity with MOFs and COFs and their functionality and porosity and perovskites superior optoelectronic properties. The CO₂ photoreduction process benefits from these combinations because they create multiphase catalytic pathways and synergistic charge separation mechanisms.

9.4 Photocatalysis under Visible and Near-Infrared Light

The spectrum needs to be made more usable for solar applications. Graphene-based composites are being designed to absorb in the visible and near-infrared spectrums by using doping techniques, plasmonic coupling, or up conversion. This increases the solar-to-fuel conversion rates and enables the effective harvesting of low-energy photons.

9.5 Integration with Solar Fuels and Artificial Photosynthesis Systems

The development of artificial photosynthesis approaches nears completion through the integration of graphene-based photocatalysts into the complete system that include photoanodes, cathodes and membrane separators. The integrated platforms enable sustainable carbon-neutral energy cycles through direct fuel production of methane or methanol from CO₂ and water by using sunlight as shown in (Fig.27)[289].

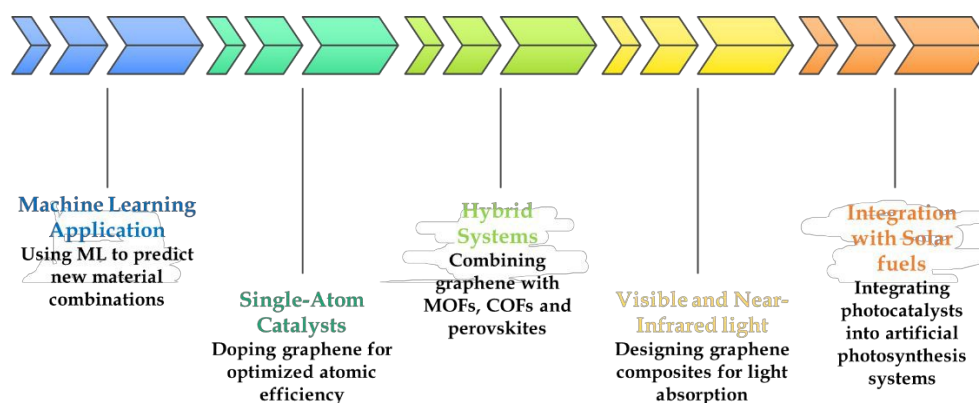


Fig. 27 Advances in photocatalysis in CO₂ reduction

10. Future Perspectives and Roadmap

10.1 Research Gaps and New Directions

The field of nanotechnology faces ongoing challenges regarding charge dynamics at the nanoscale and material stability and multifunctionality. The main research



directions for the future should focus on high-throughput screening and sophisticated in situ characterization tools and machine learning for guided material discovery.

10.2 Toward Commercial-Scale CO₂ Photoreduction

The advancement of technologies beyond the laboratory settings requires pilot-scale studies to demonstrate economic viability, dependability and integration with CO₂ capture units. The validation of real-world performance and technology scaling requires essential collaboration between academic institutions and industrial partners and government officials[290].

10.3 Policy, Funding, and Interdisciplinary Collaborations

The advancement of graphene research depends on the public and private funding initiatives which enable laboratory discoveries to become deployable technologies. Systemic innovation will emerge from interdisciplinary partnerships between materials science and chemical engineering and environmental policy and economics researchers.

10.4 Vision for Graphene-Based Nanomaterials in Climate Solutions

Graphene-based photocatalysts present a viable route for the sustainable use of CO₂. These materials can make a substantial contribution to climate mitigation by utilizing solar energy to transform greenhouse gases into useful fuels and chemicals. To achieve a carbon-neutral future, next-generation graphene hybrids and their integration into integrated energy systems will be essential as shown in (Fig.28)[291].

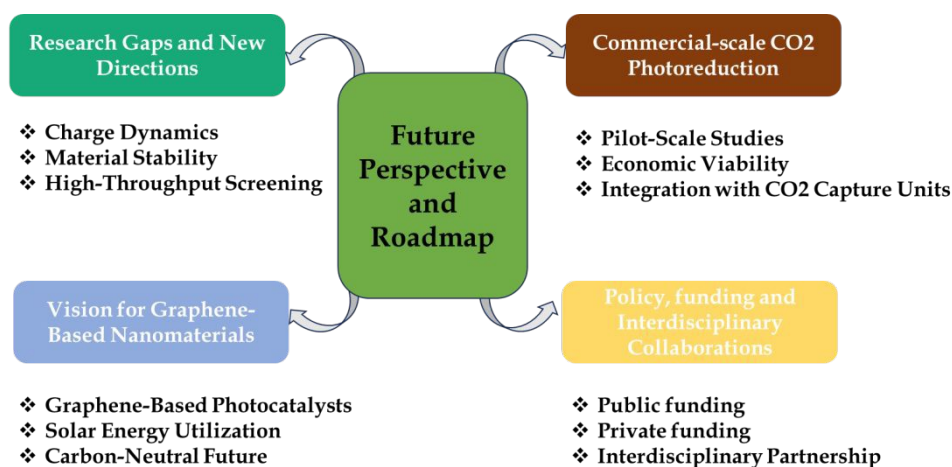


Fig. 28 Future perspective and roadmap of nanotechnology for CO₂ reduction



11. Conclusion

Photocatalytic carbon dioxide (CO₂) reduction provides a viable pathway toward sustainable energy conversion and carbon management; however, challenges with low efficiency, poor selectivity and limited stability will continue to hinder the commercialization of photocatalytic CO₂ systems. Recent advances in the field of graphene-based nanomaterials demonstrate that their remarkable capabilities (high surface area, increasing conductivity, tunable chemistry and electron mediators) can resolve many of these impediments. The incorporation of graphene into semiconductor, metal oxide, metal and carbon nitride systems has provided significant enhancements in light absorption, charge separation and inference stabilization of key intermediates during additional reactions and resultantly increased yields of CO₂ in the form of CO, CH₄, CH₃OH and HCOOH. Further advances including bandgap, Z-scheme, plasmonic enhancements and surface functionalization have illustrated the flexibility of graphene as a co-catalyst to tune the selectivity of CO₂ photoreduction, as well as to serve as a structural platform. However, there are still major challenges to overcome. Stability through long-term operation, scalability of synthesis pathways and the footprint of produced graphene at large scales are important factors that need to be addressed. Furthermore, although several reviews focus on model systems and laboratory conditions, our implementation of systems into commercial solar driven reactors remains limited. As such, the research needed to solve these technical issues will require the integration of several techniques, rational engineering of interfaces, precise control over heteroatom doping and the appropriate hybridization with metals and semiconductors, such that efficiency and selectivity can be achieved at scale. Looking forward, the combination of emerging technologies such as single-atom catalysis, machine learning-assisted catalyst design and green synthesis routes offers new opportunities for tailoring graphene-based systems toward high-performance CO₂ reduction. The synergistic integration of experimental and theoretical insights will be critical to unraveling complex reaction mechanisms and guiding the rational design of next-generation photocatalysts. With continued innovation, graphene-based



nanomaterials hold immense potential to accelerate the realization of efficient, scalable and sustainable CO₂-to-fuel conversion technologies, bridging the gap between laboratory success and practical application.

Conflicts of interest

There are no conflicts to declare.

Notes

The authors declare no competing financial interests.

Acknowledgment

Abhishek, Anas and Trupti thank to Government of Gujarat for financial support under SHODH fellowship; (File No. KCG/SHODH/2023-24/202301737, KCG/SHODH/2023-24/2022011739 and KCG/SHODH/2023-24/202301735). SKP acknowledges Tarsadia Institute of Chemical Science, Uka Tarsadia University, Surat-394350, Gujarat, India for providing the infrastructure and instrument facilities.

Author Contributions

Abhishek R. Patel: Writing – Original Draft & editing; **Anas D. Fazal:** Writing – Original Draft & editing; **Trupti D. Solanky:** Writing – Original Draft; **Subhendu Dhibar:** Writing – Original Draft. **Sumit Kumar:** Writing – Original Draft, Funding Acquisition, Resources, Supervision; **Sumit Kumar Panja:** Writing – Original Draft, Funding Acquisition, Resources, Supervision.

Author ORCID

ARP: <https://orcid.org/0009-0001-5443-6489>

ADF: <https://orcid.org/0009-0008-0112-9320>

TDS: <https://orcid.org/0009-0005-4965-0519>

SD: <https://orcid.org/0000-0002-9683-1540>

SK: <https://orcid.org/0000-0002-5695-5944>


SKP: <https://orcid.org/0000-0001-5658-0452>

References:

Uncategorized References



- [1] M. Kabir *et al.*, Climate change due to increasing concentration of carbon dioxide and its impacts on environment in 21st century; a mini review, Journal of King Saud University-Science 35 (2023) 102693.
- [2] F.S. Islam, Clean coal technology: the solution to global warming by reducing the emission of carbon dioxide and methane, American Journal of Smart Technology and Solutions 4 (2025) 8.
- [3] S. Kharchuk, From Closed-Loop Cycles to a Clean Future: Reducing CO₂ Emissions by 60-90% through Enhanced Legacy Technologies-So We Do Not Become Petrified Relics of Our Own Misjudgments, Available at SSRN 5241304 (2024).
- [4] R. Naz, M. Tahir, Recent Developments in Metal-free Materials for Photocatalytic and Electrocatalytic Carbon Dioxide Conversion into Value Added Products, Energy & Fuels 39 (2025) 6127.
- [5] L.-L. Wu, L.-Q. Yang, W.-X. Liu, T.-Y. Hang, X.-F. Yang, Research progress on photocatalysts for CO₂ conversion to liquid products, Rare Metals (2025) 1.
- [6] M. Gholami, R. Sedghi, Graphene-Based Photocatalysts for Hydrogen Production and Environmental Remediation, Springer, 2024, p. 535-562.
- [7] H. Liu, M. Yu, X. Tong, Q. Wang, M. Chen, High temperature solid oxide electrolysis for green hydrogen production, Chemical Reviews 124 (2024) 10509.
- [8] D.M.H. Pham, New and Traditional Density Functional Theory Methods for Unveiling Mechanisms of Green Chemistry Processes, (2025).
- [9] F. Zhang, J. Liu, L. Hu, C. Guo, Recent Progress of Three-Dimensional Graphene-Based Composites for Photocatalysis, Gels 10 (2024) 626.
- [10] H. Khan, Graphene based semiconductor oxide photocatalysts for photocatalytic hydrogen (H₂) production, a review, International Journal of Hydrogen Energy 84 (2024) 356.
- [11] M.R.A. Foisal, A.B. Imran, Graphene-Based Photocatalysts for Hydrogen Production and Environmental Remediation, Springer, 2024, p. 499-534.
- [12] J. Low, J. Yu, W. Ho, Graphene-based photocatalysts for CO₂ reduction to solar fuel, The journal of physical chemistry letters 6 (2015) 4244.
- [13] Y.-H. Chen, J.-K. Ye, Y.-J. Chang, T.-W. Liu, Y.-H. Chuang, W.-R. Liu, S.-H. Liu, Y.-C. Pu, Mechanisms behind photocatalytic CO₂ reduction by CsPbBr₃ perovskite-



- graphene-based nanoheterostructures, *Applied Catalysis B: Environmental* 284 (2021) 119751.
- [14] A. Sewnet, M. Abebe, P. Asaithambi, E. Alemayehu, Visible-light-driven g-C₃N₄/TiO₂ based heterojunction nanocomposites for photocatalytic degradation of organic dyes in wastewater: a review, *Air, Soil and Water Research* 15 (2022) 11786221221117266.
- [15] S.B. Nehru, N. Perumal, Y.P. Subbarayalu, Sustainable water treatment: Synthesis and characterization of g-C₃N₅/NiCo₂S₄ heterojunction nanocomposite for efficient visible light-induced degradation of highly hazardous organic pollutants, *Journal of Water Process Engineering* 73 (2025) 107712.
- [16] P. Kyokunzire, G. Jeong, S.Y. Shin, H.J. Cheon, E. Wi, M. Woo, T.T. Vu, M. Chang, Enhanced nitric oxide sensing performance of conjugated polymer films through incorporation of graphitic carbon nitride, *International Journal of Molecular Sciences* 24 (2023) 1158.
- [17] M.A. Ahmed, S.A. Mahmoud, A.A. Mohamed, Unveiling the photocatalytic potential of graphitic carbon nitride (gC₃N₄): a state-of-the-art review, *RSC advances* 14 (2024) 25629.
- [18] L. Wang, J. Yu, *Interface science and technology*, Elsevier, 2023, p. 1-52.
- [19] J. Kim, K. Lee, S. Choi, N. Jo, Y.S. Nam, Catechol Quinone as an Electron-Shuttling Spot Conjugated to Graphitic Carbon Nitride for Enhancing Photocatalytic Reduction, *Chemistry of Materials* 36 (2024) 5037.
- [20] M. Aresta, A. Dibenedetto, A. Angelini, Catalysis for the valorization of exhaust carbon: from CO₂ to chemicals, materials, and fuels. Technological use of CO₂, *Chemical reviews* 114 (2014) 1709.
- [21] M.Z. Rahman, C.B. Mullins, Understanding charge transport in carbon nitride for enhanced photocatalytic solar fuel production, *Accounts of chemical research* 52 (2018) 248.
- [22] D. Qin *et al.*, Recent advances in two-dimensional nanomaterials for photocatalytic reduction of CO₂: insights into performance, theories and perspective, *Journal of materials chemistry A* 8 (2020) 19156.


View Article Online
DOI: 10.1039/D5MA00750J



- [23] Y. Guo, S. Zhong, J. Huang, CO₂ Photo/Electro-Conversion Mechanism, CO₂ Conversion and Utilization: Photocatalytical and Electrochemical Methods and Applications (2023) 17.
- [24] P. Kalra, C.M. Suresh, N. Rashid, P.P. Ingole, 5 Photoelectrocatalytic Carbon Dioxide, Photoelectrochemical Generation of Fuels (2022) 149.
- [25] R. Gandhi, A. Moses, S.S. Baral, Fundamental study of the photocatalytic reduction of CO₂: A short review of thermodynamics, kinetics and mechanisms, Chemical and Process Engineering 43 (2022) 223.
- [26] L. Liu, S. Wang, H. Huang, Y. Zhang, T. Ma, Surface sites engineering on semiconductors to boost photocatalytic CO₂ reduction, Nano Energy 75 (2020) 104959.
- [27] B. Petrovic, M. Gorbounov, S.M. Soltani, Influence of surface modification on selective CO₂ adsorption: A technical review on mechanisms and methods, Microporous and mesoporous materials 312 (2021) 110751.
- [28] X. Wang, F. Wang, Y. Sang, H. Liu, Full-spectrum solar-light-activated photocatalysts for light-chemical energy conversion, Advanced Energy Materials 7 (2017) 1700473.
- [29] A. Nawaz, A. Kuila, N.S. Mishra, K.H. Leong, L.C. Sim, P. Saravanan, M. Jang, Challenges and implication of full solar spectrum-driven photocatalyst, Reviews in Chemical Engineering 37 (2021) 533.
- [30] S. Peiris, H.B. de Silva, K.N. Ranasinghe, S.V. Bandara, I.R. Perera, Recent development and future prospects of TiO₂ photocatalysis, Journal of the Chinese Chemical Society 68 (2021) 738.
- [31] C. Hiragond, N. Powar, J. Lee, S.I. In, Single-Atom Catalysts (SACs) for Photocatalytic CO₂ Reduction with H₂O: Activity, Product Selectivity, Stability, and Surface Chemistry, Small 18 (2022). <https://doi.org/10.1002/smll.202201428>
- [32] G.Z.S. Ling, S.F. Ng, W.J. Ong, Tailor-engineered 2D cocatalysts: harnessing electron-hole redox center of 2D g-C₃N₄ photocatalysts toward solar-to-chemical conversion and environmental purification, Advanced Functional Materials 32 (2022) 2111875.




- [33] K. Huang, C. Li, H. Li, G. Ren, L. Wang, W. Wang, X. Meng, Photocatalytic applications of two-dimensional Ti₃C₂ MXenes: a review, *ACS Applied Nano Materials* 3 (2020) 9581.
- [34] J. Ma, T.J. Miao, J. Tang, Charge carrier dynamics and reaction intermediates in heterogeneous photocatalysis by time-resolved spectroscopies, *Chemical Society Reviews* 51 (2022) 5777.
- [35] S. Bhattacharyya, *Carbon Superstructures: From Quantum Transport to Quantum Computation*. CRC Press, 2024.
- [36] G.R. Bhimanapati *et al.*, Recent advances in two-dimensional materials beyond graphene, *ACS nano* 9 (2015) 11509.
- [37] T. Enoki, Y. Kobayashi, K.-I. Fukui, Electronic structures of graphene edges and nanographene, *International Reviews in Physical Chemistry* 26 (2007) 609.
- [38] Z. Zhen, H. Zhu, *Graphene*, Elsevier, 2018, p. 1-12.
- [39] R. Geetha Bai, K. Muthoosamy, S. Manickam, A. Hilal-Alnaqbi, Graphene-based 3D scaffolds in tissue engineering: fabrication, applications, and future scope in liver tissue engineering, *International Journal of Nanomedicine* 14 (2019). <https://doi.org/10.2147/IJN.S192779>
- [40] A. Kaplan, Z. Yuan, J.D. Benck, A.G. Rajan, X.S. Chu, Q.H. Wang, M.S. Strano, Current and future directions in electron transfer chemistry of graphene, *Chemical Society Reviews* 46 (2017) 4530.
- [41] N. Zhang, M.-Q. Yang, S. Liu, Y. Sun, Y.-J. Xu, Waltzing with the versatile platform of graphene to synthesize composite photocatalysts, *Chemical reviews* 115 (2015) 10307.
- [42] H. Grajek, J. Jonik, Z. Witkiewicz, T. Wawer, M. Purchała, Applications of graphene and its derivatives in chemical analysis, *Critical Reviews in Analytical Chemistry* 50 (2020) 445.
- [43] C. Li, C. Zheng, F. Cao, Y. Zhang, X. Xia, The development trend of graphene derivatives, *Journal of Electronic Materials* 51 (2022) 4107.
- [44] J. Narayan, K. Bezborah, Recent advances in the functionalization, substitutional doping and applications of graphene/graphene composite nanomaterials, *RSC advances* 14 (2024) 13413.



- 1398 [45] R. Ghosh, M. Aslam, H. Kalita, Graphene derivatives for chemiresistive gas
1399 sensors: A review, *Materials Today Communications* 30 (2022) 103182.
- 1400 [46] R. Singh *et al.*, Synthesis of Three-Dimensional Reduced-Graphene Oxide from
1401 Graphene Oxide, *Journal of Nanomaterials* 2022 (2022) 8731429.
- 1402 [47] A. Ahmed, A. Singh, S.-J. Young, V. Gupta, M. Singh, S. Arya, Synthesis
1403 techniques and advances in sensing applications of reduced graphene oxide (rGO)
1404 Composites: A review, *Composites Part A: Applied Science and Manufacturing* 165
1405 (2023) 107373.
- 1406 [48] A. Mondal, A. Prabhakaran, S. Gupta, V.R. Subramanian, Boosting photocatalytic
1407 activity using reduced graphene oxide (RGO)/ semiconductor nanocomposites: issues
1408 and future scope, *ACS omega* 6 (2021) 8734.
- 1409 [49] P. Jadhav, G.M. Joshi, Recent trends in Nitrogen doped polymer composites: a
1410 review, *Journal of Polymer Research* 28 (2021) 73. [https://doi.org/10.1007/s10965-](https://doi.org/10.1007/s10965-021-02436-x)
1411 [021-02436-x](https://doi.org/10.1007/s10965-021-02436-x)
- 1412 [50] N. Sohal, B. Maity, S. Basu, Recent advances in heteroatom-doped graphene
1413 quantum dots for sensing applications, *RSC advances* 11 (2021) 25586.
- 1414 [51] M.B. Arvas, H. Gürsu, M. Gencten, Y. Sahin, Preparation of different heteroatom
1415 doped graphene oxide based electrodes by electrochemical method and their
1416 supercapacitor applications, *Journal of Energy Storage* 35 (2021) 102328.
- 1417 [52] S.J. Lee *et al.*, Heteroatom-doped graphene-based materials for sustainable energy
1418 applications: A review, *Renewable and Sustainable Energy Reviews* 143 (2021) 110849.
- 1419 [53] F. Zhang, E. Alhajji, Y. Lei, N. Kurra, H.N. Alshareef, Highly doped 3D graphene
1420 Na-ion battery anode by laser scribing polyimide films in nitrogen ambient, *Advanced*
1421 *Energy Materials* 8 (2018) 1800353.
- 1422 [54] E. Umar, M. Ikram, J. Haider, W. Nabgan, M. Imran, G. Nazir, 3D graphene-based
1423 material: Overview, perspective, advancement, energy storage, biomedical
1424 engineering and environmental applications a bibliometric analysis, *Journal of*
1425 *Environmental Chemical Engineering* 11 (2023) 110339.
1426 [https://doi.org/https://doi.org/10.1016/j.jece.2023.110339](https://doi.org/10.1016/j.jece.2023.110339)


View Article Online
DOI: 10.1039/D3MA00750J



- [55] F.M. Vivaldi *et al.*, Three-dimensional (3D) laser-induced graphene: structure, properties, and application to chemical sensing, *ACS Applied Materials & Interfaces* 13 (2021) 30245.
- [56] W. Xiao, B. Li, J. Yan, L. Wang, X. Huang, J. Gao, Three dimensional graphene composites: preparation, morphology and their multi-functional applications, *Composites Part A: Applied Science and Manufacturing* 165 (2023) 107335.
- [57] A.M. Díez-Pascual, MDPI, 2021, p. 7726.
- [58] A. Hussain, Y. Weng, Y. Huang, Graphene and graphene-based nanomaterials: current applications and future perspectives, *Drug Delivery Using Nanomaterials* (2022) 209.
- [59] A. Gutiérrez-Cruz, A.R. Ruiz-Hernández, J.F. Vega-Clemente, D.G. Luna-Gazcón, J. Campos-Delgado, A review of top-down and bottom-up synthesis methods for the production of graphene, graphene oxide and reduced graphene oxide, *Journal of Materials Science* 57 (2022) 14543. <https://doi.org/10.1007/s10853-022-07514-z>
- [60] E. Boateng, A.R. Thirupathi, C.-K. Hung, D. Chow, D. Sridhar, A. Chen, Functionalization of graphene-based nanomaterials for energy and hydrogen storage, *Electrochimica Acta* 452 (2023) 142340.
- [61] D.S. Rakshe, P. William, M. Jawale, A. Pawar, S.K. Korde, N. Deshpande, Synthesis and characterization of graphene based nanomaterials for energy applications, (2023).
- [62] J.M. Tour, Top-down versus bottom-up fabrication of graphene-based electronics, *Chemistry of Materials* 26 (2014) 163.
- [63] A.L. Olatomiwa, T. Adam, S.C. Gopinath, S.Y. Kolawole, O.H. Olayinka, U. Hashim, Graphene synthesis, fabrication, characterization based on bottom-up and top-down approaches: An overview, *Journal of Semiconductors* 43 (2022) 061101.
- [64] R. Boddula, N. Borane, N. Odedara, J. Singh, *Graphene-Based Nanomaterials*, CRC Press, 2024, p. 33-46.
- [65] H. Jiang, Chemical preparation of graphene-based nanomaterials and their applications in chemical and biological sensors, *Small* 7 (2011) 2413.
- [66] N. Borane, S. Aralekallu, R. Boddula, J. Singh, M.D. Kurkuri, *Carbon-Based Nanomaterials in Biosystems*, Elsevier, 2024, p. 91-120.




- [67] B.C. Brodie, XIII. On the atomic weight of graphite, Philosophical transactions of the Royal Society of London (1859) 249.
- [68] D.C. Marcano *et al.*, Improved synthesis of graphene oxide, ACS nano 4 (2010) 4806.
- [69] H.L. Poh, F. Šaněk, A. Ambrosi, G. Zhao, Z. Sofer, M. Pumera, Graphenes prepared by Staudenmaier, Hofmann and Hummers methods with consequent thermal exfoliation exhibit very different electrochemical properties, Nanoscale 4 (2012) 3515.
- [70] L. Shahriary, A.A. Athawale, Graphene oxide synthesized by using modified hummers approach, Int. j. renew. energy environ. eng 2 (2014) 58.
- [71] T. Dzhabiev, N. Denisov, D. Moiseev, A. Shilov, Formation of ozone during the reduction of potassium permanganate in sulfuric acid solutions, Russian Journal of Physical Chemistry A 79 (2005) 1755.
- [72] W. Gao *et al.*, Ozonated graphene oxide film as a proton-exchange membrane, Angewandte Chemie International Edition 53 (2014) 3588.
- [73] M. Muradov, E. Huseynov, M. Conradi, M. Malok, T. Sever, M.B. Baghirov, Effects of gamma radiation on the properties of GO/PVA/AgNW nanocomposites, RSC Advances 15 (2025) 13574. <https://doi.org/10.1039/D5RA01344E>
- [74] S.K. Sharma, S. Sharma, Synthesis of Graphene Oxide and Impact of Its Functionalization in the Wastewater Treatment, Chemical Engineering & Technology 48 (2025) e70009. <https://doi.org/10.1002/ceat.70009>
- [75] C. Han, M.-Q. Yang, N. Zhang, Y.-J. Xu, Enhancing the visible light photocatalytic performance of ternary CdS-(graphene-Pd) nanocomposites via a facile interfacial mediator and co-catalyst strategy, Journal of Materials Chemistry A 2 (2014) 19156.
- [76] Y. Li, Z. Zhang, L. Pei, X. Li, T. Fan, J. Ji, J. Shen, M. Ye, Multifunctional photocatalytic performances of recyclable Pd-NiFe₂O₄/reduced graphene oxide nanocomposites via different co-catalyst strategy, Applied Catalysis B: Environmental 190 (2016) 1.
- [77] D. Maarisetty, S.S. Baral, Synergistic effect of dual electron-cocatalyst modified photocatalyst and methodical strategy for better charge separation, Applied Surface Science 489 (2019) 930.




- [78] R. Akhter, S. Hussain, S.S. Maktedar, Advanced graphene-based (photo & electro) catalysts for sustainable & clean energy technologies, *New Journal of Chemistry* 48 (2024) 437.
- [79] L. Ye, J. Fu, Z. Xu, R. Yuan, Z. Li, Facile one-pot solvothermal method to synthesize sheet-on-sheet reduced graphene oxide (RGO)/ZnIn₂S₄ nanocomposites with superior photocatalytic performance, *ACS applied materials & interfaces* 6 (2014) 3483.
- [80] N. Meng, Y. Zhou, W. Nie, P. Chen, Synthesis of CdS-decorated RGO nanocomposites by reflux condensation method and its improved photocatalytic activity, *Journal of Nanoparticle Research* 18 (2016) 1. <https://doi.org/10.1007/s11051-016-3522-y>
- [81] J. Prakash, Mechanistic insights into graphene oxide driven photocatalysis as Co-catalyst and sole catalyst in degradation of organic dye pollutants, *Photochem* 2 (2022) 651.
- [82] F. Khan, M.S. Khan, S. Kamal, M. Arshad, S.I. Ahmad, S.A. Nami, Recent advances in graphene oxide and reduced graphene oxide based nanocomposites for the photodegradation of dyes, *Journal of Materials Chemistry C* 8 (2020) 15940.
- [83] A. Mondal, A. Vomiero, 2D transition metal dichalcogenides-based electrocatalysts for hydrogen evolution reaction, *Advanced Functional Materials* 32 (2022) 2208994.
- [84] N.H. Shudin, M. Aziz, M.H.D. Othman, M. Tanemura, M.Z.M. Yusop, The role of solid, liquid and gaseous hydrocarbon precursors on chemical vapor deposition grown carbon nanomaterials' growth temperature, *Synthetic Metals* 274 (2021) 116735.
- [85] P. Chavalekvirat, W. Hirunpinyopas, K. Deshsorn, K. Jitapunkul, P. Iamprasertkun, Liquid phase exfoliation of 2D materials and its electrochemical applications in the data-driven future, *Precision Chemistry* 2 (2024) 300.
- [86] T. HUANG, F. Bing, L. Peipei, Z. ZHANG, N. Qi, M. Zonghu, L. Kai, L. Qiang, Hydrothermal N-doping assisted synthesis of poplar sawdust-derived porous carbons for carbon capture, *Journal of Fuel Chemistry and Technology* 53 (2025) 1191.
- [87] N. Zhang, Y. Zhang, Y.-J. Xu, Recent progress on graphene-based photocatalysts: current status and future perspectives, *Nanoscale* 4 (2012) 5792.



- [88] X. An, C.Y. Jimmy, Graphene-based photocatalytic composites, *Rsc Advances* 1 (2011) 1426.
- [89] F. Saeedi, R. Ansari, M. Haghgoo, Recent Advances of Graphene-Based Wearable Sensors: Synthesis, Fabrication, Performance, and Application in Smart Device, *Advanced Materials Interfaces* (2025) 2500093.
- [90] B.C. Yallur *et al.*, Recent Advances in Graphene-Based Metal Oxide Composites for Supercapacitors: A Comprehensive Review, *Advanced Sustainable Systems* 2500121.
- [91] H.S. Biswas, A.K. Kundu, S.S. Biswas, Recent Advancement of Graphene-TiO₂ Composite Nanomaterials and Their Applications in Energy Storage and Conversion: Novel Functions and Future Prospects Explored, *Innovations in Next-Generation Energy Storage Solutions* (2025) 425.
- [92] Y. Zhang, H. Wang, J. Zhang, Application of Graphene-Based Solar Driven Interfacial Evaporation-Coupled Photocatalysis in Water Treatment, *Catalysts* 15 (2025) 336.
- [93] T. Shahzad, S. Nawaz, H. Jamal, T. Shahzad, F. Akhtar, U. Kamran, A Review on Cutting-Edge Three-Dimensional Graphene-Based Composite Materials: Redefining Wastewater Remediation for a Cleaner and Sustainable World, *Journal of Composites Science* 9 (2025) 18.
- [94] A. Badoni *et al.*, Recent progress in understanding the role of graphene oxide, TiO₂ and graphene oxide-TiO₂ nanocomposites as multidisciplinary photocatalysts in energy and environmental applications, *Catalysis Science & Technology* (2025).
- [95] Y. Wu, C. Wang, L. Wang, C. Hou, Recent Advances in Iron Oxide-Based Heterojunction Photo-Fenton Catalysts for the Elimination of Organic Pollutants, *Catalysts* 15 (2025) 391.
- [96] A.K. Potbhare *et al.*, Bioinspired graphene-based metal oxide nanocomposites for photocatalytic and electrochemical performances: an updated review, *Nanoscale Advances* 6 (2024) 2539.
- [97] T. Xu, J. Wang, X. Yu, Y. Niu, H. Li, Y. Wu, M. Li, J. Rong, A new generation of functional desalted carbon and nitrogen membrane with photocatalytic and adsorption properties, *Computational Materials Science* 258 (2025) 114014.




- [98] A. Khalajolyaie, C. Jian, *Advances in Graphene-Based Materials for Metal Ion Sensing and Wastewater Treatment: A Review*, *Environments* 12 (2025) 43.
- [99] W. Gao, H. Chi, Y. Xiong, J. Ye, Z. Zou, Y. Zhou, Comprehensive insight into construction of active sites toward steering photocatalytic CO₂ conversion, *Advanced Functional Materials* 34 (2024) 2312056.
- [100] S. Wang, M. Xu, T. Peng, C. Zhang, T. Li, I. Hussain, J. Wang, B. Tan, Porous hypercrosslinked polymer-TiO₂-graphene composite photocatalysts for visible-light-driven CO₂ conversion, *Nature communications* 10 (2019) 676.
- [101] F.-X. Liang, Y. Gao, C. Xie, X.-W. Tong, Z.-J. Li, L.-B. Luo, Recent advances in the fabrication of graphene-ZnO heterojunctions for optoelectronic device applications, *Journal of Materials Chemistry C* 6 (2018) 3815.
- [102] S. Chandrasekaran, J.S. Chung, E.J. Kim, S.H. Hur, Exploring complex structural evolution of graphene oxide/ZnO triangles and its impact on photoelectrochemical water splitting, *Chemical Engineering Journal* 290 (2016) 465.
- [103] X. Li, J. Yu, M. Jaroniec, X. Chen, Cocatalysts for selective photoreduction of CO₂ into solar fuels, *Chemical reviews* 119 (2019) 3962.
- [104] P.M. Gawal, J. Ishrat, K. Bhattacharyya, A.K. Golder, Experimental and Theoretical Studies on Photocatalytic CO₂ Reduction to HCOOH by Biomass-Derived Carbon Dots Embedded Phytochemical-Based CdS Quantum Dots, *Langmuir* (2025).
- [105] H.V. Babu, M.M. Bai, M. Rajeswara Rao, Functional π -conjugated two-dimensional covalent organic frameworks, *ACS applied materials & interfaces* 11 (2019) 11029.
- [106] L. Jing, P. Li, Z. Li, D. Ma, J. Hu, Influence of π - π interactions on organic photocatalytic materials and their performance, *Chemical Society Reviews* (2025).
- [107] Y. Li, L. Wang, X. Gao, Y. Xue, B. Li, X. Zhu, Construction of a graphitic carbon nitride-based photocatalyst with a strong built-in electric field via π - π stacking interactions boosting photocatalytic CO₂ reduction, *Journal of Materials Chemistry A* 12 (2024) 7807.
- [108] K. Jayaramulu *et al.*, Graphene-based metal-organic framework hybrids for applications in catalysis, environmental, and energy technologies, *Chemical reviews* 122 (2022) 17241.



- [109] J. Yang, Z. Chen, L. Zhang, Q. Zhang, Covalent organic frameworks for photocatalytic reduction of carbon dioxide: A review, *ACS nano* 18 (2024) 21804.
- [110] I. Ahmad *et al.*, Recent progress in ZnO-based heterostructured photocatalysts: A review, *Materials Science in Semiconductor Processing* 180 (2024) 108578. <https://doi.org/https://doi.org/10.1016/j.mssp.2024.108578>
- [111] I. Ahmad, S. Shukrullah, M.Y. Naz, H.N. Bhatti, Dual S-scheme ZnO-g-C₃N₄-CuO heterosystem: a potential photocatalyst for H₂ evolution and wastewater treatment, *Reaction Chemistry & Engineering* 8 (2023) 1159. <https://doi.org/10.1039/D2RE00576J>
- [112] I. Ahmad, S. Shukrullah, M.Y. Naz, H.N. Bhatti, A Cu medium designed Z-scheme ZnO-Cu-CdS heterojunction photocatalyst for stable and excellent H₂ evolution, methylene blue degradation, and CO₂ reduction, *Dalton Transactions* 52 (2023) 6343. <https://doi.org/10.1039/D3DT00684K>
- [113] I. Ahmad, S.A. AlFaify, K.M. Alanezi, M.Q. Alfaifi, M.M. Abduljawad, Y. Liu, Improved hydrogen production performance of an S-scheme Nb₂O₅/La₂O₃ photocatalyst, *Dalton Transactions* 54 (2025) 1402. <https://doi.org/10.1039/D4DT02913E>
- [114] I. Ahmad *et al.*, Boosted hydrogen evolution activity from Sr doped ZnO/CNTs nanocomposite as visible light driven photocatalyst, *International Journal of Hydrogen Energy* 46 (2021) 26711. <https://doi.org/https://doi.org/10.1016/j.ijhydene.2021.05.164>
- [115] I. Ahmad, M.Q. Alfaifi, S. Ben Ahmed, M.M. Abduljawad, Y.A. Alassmy, S.A. Alshuhri, T.L. Tamang, Strategies for optimizing sunlight conversion in semiconductor photocatalysts: A review of experimental and theoretical insights, *International Journal of Hydrogen Energy* 96 (2024) 1006. <https://doi.org/https://doi.org/10.1016/j.ijhydene.2024.11.388>
- [116] M.T. Vu, D. Thatikayala, B. Min, Porous reduced-graphene oxide supported hollow titania (rGO/TiO₂) as an effective catalyst for upgrading electromethanogenesis, *International Journal of Hydrogen Energy* 47 (2022) 1121.
- [117] J. Wu, M. Gong, ZnO/graphene heterostructure nanohybrids for optoelectronics and sensors, *Journal of Applied Physics* 130 (2021).




- [118] Z. Tan, R. Wang, S. Yang, Z. Shi, D. Wang, Fabrication of Cu-Cu₂ON doped carbon with high photo-Fenton catalytic activity using a Cu-nicotinic acid framework: Insight into structural transformation, *Journal of Molecular Structure* 1337 (2025) 142248.
- [119] R. CHATURVEDI, R. PANDEY, S. SINGHANIA, A. GARG, Synergic Energy Storage Performance of MoS₂/g-C₃N₄ composite on Screen-printed Carbon Electrode, *Electrochimica Acta* (2025) 147090.
- [120] G. Bharath *et al.*, Synthesis of TiO₂/RGO with plasmonic Ag nanoparticles for highly efficient photoelectrocatalytic reduction of CO₂ to methanol toward the removal of an organic pollutant from the atmosphere, *Environmental Pollution* 281 (2021) 116990.
- [121] J. Wekalao, High-sensitivity graphene-MoS₂ hybrid metasurface biosensor with machine learning optimization for hemoglobin detection, *Plasmonics* (2025) 1.
- [122] D. Kanakaraju, D.N. Joseph, P.P. Natashya, A. Pace, Pioneering TiO₂/G-C₃N₄ Heterostructures for Enhanced Organic Pollutant Removal, *ChemistrySelect* 10 (2025) e202405101.
- [123] S.K. Behura, C. Wang, Y. Wen, V. Berry, Graphene-semiconductor heterojunction sheds light on emerging photovoltaics, *Nature Photonics* 13 (2019) 312.
- [124] A. Di Bartolomeo, Graphene Schottky diodes: An experimental review of the rectifying graphene/semiconductor heterojunction, *Physics Reports* 606 (2016) 1.
- [125] Z. Zhu, I. Murtaza, H. Meng, W. Huang, Thin film transistors based on two dimensional graphene and graphene/semiconductor heterojunctions, *RSC advances* 7 (2017) 17387.
- [126] S. Behura, C. Wang, Y. Wen, V. Berry, Graphene-Semiconductor Heterojunction Sheds Light on Emerging Photovoltaics, *Nature Photonics* 13 (2019). <https://doi.org/10.1038/s41566-019-0391-9>
- [127] Y.-J. Kim, J.-H. Lee, G.-C. Yi, Vertically aligned ZnO nanostructures grown on graphene layers, *Applied Physics Letters* 95 (2009) 213101. <https://doi.org/10.1063/1.3266836>
- [128] D. Maeso, A. Castellanos-Gomez, N. Agraït, G. Rubio-Bollinger, Fast Yet Quantum-Efficient Few-Layer Vertical MoS₂ Photodetectors, *Advanced Electronic*




- 1644 Materials 5 (2019) 1900141. <https://doi.org/10.1002/aelm.201900141>
- 1645 <https://doi.org/10.1002/aelm.201900141>
- 1646 [129] X. Ge, W. Qin, H. Zhang, G. Wang, Y. Zhang, C. Yu, A three-dimensional porous
1647 Co@C/carbon foam hybrid monolith for exceptional oil–water separation, *Nanoscale*
1648 11 (2019) 12161. <https://doi.org/10.1039/C9NR02819F>
- 1649 [130] X. Xu, X. Zhang, C. Hu, Y. Zheng, B. Lei, Y. Liu, J. Zhuang, Construction of
1650 NaYF₄:Yb,Er(Tm)@CDs composites for enhancing red and NIR upconversion
1651 emission, *Journal of Materials Chemistry C* 7 (2019) 6231.
1652 <https://doi.org/10.1039/C9TC01346F>
- 1653 [131] A. Singh, S. Chahal, H. Dahiya, A. Goswami, S. Nain, Synthesis of Ag
1654 nanoparticle supported graphene/multi-walled carbon nanotube based nanohybrids
1655 for photodegradation of toxic dyes, *Materials Express* 11 (2021) 936.
- 1656 [132] A. Singh, S. Chahal, H. Dahiya, A. Goswami, S. Nain, *Materials Express*,
1657 *Synthesis* 4 (2021) 4.
- 1658 [133] Q. Ding, B. Song, P. Xu, S. Jin, Efficient electrocatalytic and photoelectrochemical
1659 hydrogen generation using MoS₂ and related compounds, *Chem* 1 (2016) 699.
- 1660 [134] D. Vikraman, K. Akbar, S. Hussain, G. Yoo, J.-Y. Jang, S.-H. Chun, J. Jung, H.J.
1661 Park, Direct synthesis of thickness-tunable MoS₂ quantum dot thin layers: Optical,
1662 structural and electrical properties and their application to hydrogen evolution, *Nano*
1663 *Energy* 35 (2017) 101.
- 1664 [135] S. Chen, Y. Pan, Enhancing catalytic properties of noble metal@ MoS₂/WS₂
1665 heterojunction for the hydrogen evolution reaction, *Applied Surface Science* 591
1666 (2022) 153168.
- 1667 [136] D. Zheng, G. Zhang, Y. Hou, X. Wang, Layering MoS₂ on soft hollow g-C₃N₄
1668 nanostructures for photocatalytic hydrogen evolution, *Applied Catalysis A: General*
1669 521 (2016) 2.
- 1670 [137] Z. Wang, J. Huang, J. Mao, Q. Guo, Z. Chen, Y. Lai, Metal–organic frameworks
1671 and their derivatives with graphene composites: preparation and applications in
1672 electrocatalysis and photocatalysis, *Journal of Materials Chemistry A* 8 (2020) 2934.
- 1673 [138] E.F. Joel, G. Lujanienė, Progress in graphene oxide hybrids for environmental
1674 applications, *Environments* 9 (2022) 153.



- [139] Y.-J. Park, H. Lee, H.L. Choi, M.C. Tapia, C.Y. Chuah, T.-H. Bae, Mixed-dimensional nanocomposites based on 2D materials for hydrogen storage and CO₂ capture, *npj 2D Materials and Applications* 7 (2023) 61.
- [140] T. Zhou *et al.*, Polyethyleneimine-induced in-situ chemical epitaxial growth ultrathin 2D/2D graphene carbon nitride intralayer heterojunction with elevating photocatalytic activity: Performances and mechanism insight, *International Journal of Hydrogen Energy* 51 (2024) 884.
- [141] T.A. Shifa, F. Wang, Y. Liu, J. He, Heterostructures Based on 2D Materials: A Versatile Platform for Efficient Catalysis, *Advanced Materials* 31 (2018) 1804828. <https://doi.org/10.1002/adma.201804828>
- [142] H. Bomeriame *et al.*, Graphitic carbon nitride/few-layer graphene heterostructures for enhanced visible-LED photocatalytic hydrogen generation, *International Journal of Hydrogen Energy* 47 (2022) 25555.
- [143] H. Li, B. Zhu, B. Cheng, G. Luo, J. Xu, S. Cao, Single-atom Cu anchored on N-doped graphene/carbon nitride heterojunction for enhanced photocatalytic H₂O₂ production, *Journal of Materials Science & Technology* 161 (2023) 192.
- [144] M. Chen, M. Li, S.L.J. Lee, X. Zhao, S. Lin, Constructing novel graphitic carbon nitride-based nanocomposites-from the perspective of material dimensions and interfacial characteristics, *Chemosphere* 302 (2022) 134889.
- [145] D. Adekoya, S. Zhang, M. Hankel, 1D/2D C₃N₄/graphene composite as a preferred anode material for lithium ion batteries: importance of heterostructure design via DFT computation, *ACS applied materials & interfaces* 12 (2020) 25875.
- [146] K. Sridharan, S. Shenoy, S.G. Kumar, C. Terashima, A. Fujishima, S. Pitchaimuthu, Advanced two-dimensional heterojunction photocatalysts of stoichiometric and non-stoichiometric bismuth oxyhalides with graphitic carbon nitride for sustainable energy and environmental applications, *Catalysts* 11 (2021) 426.
- [147] X. Li *et al.*, 2D-1D-2D multi-interfacial-electron transfer scheme enhanced g-C₃N₄/MWNTs/rGO hybrid composite for accelerating CO₂ photoreduction, *Journal of Alloys and Compounds* 940 (2023) 168796.




- 1704 [148] J. Jia, Q. Zhang, K. Li, Y. Zhang, E. Liu, X. Li, Recent advances on g-C₃N₄-based
 1705 Z-scheme photocatalysts: Structural design and photocatalytic applications,
 1706 International Journal of Hydrogen Energy 48 (2023) 196.
- 1707 [149] X. Zeng, Z. Wang, G. Wang, T.R. Gengenbach, D.T. McCarthy, A. Deletic, J. Yu,
 1708 X. Zhang, Highly dispersed TiO₂ nanocrystals and WO₃ nanorods on reduced
 1709 graphene oxide: Z-scheme photocatalysis system for accelerated photocatalytic water
 1710 disinfection, Applied Catalysis B: Environmental 218 (2017) 163.
- 1711 [150] J. Low, C. Jiang, B. Cheng, S. Wageh, A.A. Al-Ghamdi, J. Yu, A review of direct
 1712 Z-scheme photocatalysts, Small methods 1 (2017) 1700080.
- 1713 [151] X. Miao, X. Shen, J. Wu, Z. Ji, J. Wang, L. Kong, M. Liu, C. Song, Fabrication of
 1714 an all solid Z-scheme photocatalyst g-C₃N₄/GO/AgBr with enhanced visible light
 1715 photocatalytic activity, Applied Catalysis A: General 539 (2017) 104.
- 1716 [152] Z. Qian, B. Pathak, J. Nisar, R. Ahuja, Oxygen-and nitrogen-chemisorbed carbon
 1717 nanostructures for Z-scheme photocatalysis applications, Journal of nanoparticle
 1718 research 14 (2012) 895.
- 1719 [153] D. Zhou, D. Li, Z. Chen, Recent advances in ternary Z-scheme photocatalysis on
 1720 graphitic carbon nitride based photocatalysts, Frontiers in Chemistry 12 (2024)
 1721 1359895. <https://doi.org/10.3389/fchem.2024.1359895>
- 1722 [154] M. Li *et al.*, Novel Z-scheme visible-light photocatalyst based on
 1723 CoFe₂O₄/BiOBr/Graphene composites for organic dye degradation and Cr (VI)
 1724 reduction, Applied Surface Science 478 (2019) 744.
- 1725 [155] W. Li, X. Wang, M. Li, S.-a. He, Q. Ma, X. Wang, Construction of Z-scheme and
 1726 pn heterostructure: Three-dimensional porous g-C₃N₄/graphene oxide-Ag/AgBr
 1727 composite for high-efficient hydrogen evolution, Applied Catalysis B: Environmental
 1728 268 (2020) 118384.
- 1729 [156] Z. Chen, S. Sun, J. Prakash, Design and engineering of graphene nanostructures
 1730 as independent solar-driven photocatalysts for emerging applications in the field of
 1731 energy and environment, Molecular Systems Design & Engineering 7 (2022) 213.
- 1732 [157] S. Huang, M. Hu, L. He, S. Ren, X. Wu, S. Cui, Construction of manganese
 1733 ferrite/zinc ferrite anchored graphene-based hierarchical aerogel photocatalysts




- 1734 following Z-scheme electron transfer for visible-light-driven carbon dioxide
 1735 reduction, *Journal of Colloid and Interface Science* (2025) 137678.
- 1736 [158] U. C Gowda, H. Priyadarshini, K. Prashantha, M. Shkir, S. Appu, G. Nagaraju,
 1737 S.G. Kumar, Enhanced Photocatalytic Performances of Ag-BiVO₄/TiO₂@ Graphene-
 1738 Based Z-Scheme Heterojunction.
- 1739 [159] M. Chu, J. Bian, Z. Zhang, Z. Zhao, L. Jing, Graphene-Regulated Interfacial Z-
 1740 Scheme Charge Transfer for CO₂ Photoreduction to CO with Nearly 100% Selectivity,
 1741 *The Journal of Physical Chemistry C* (2025).
- 1742 [160] M.T. Baig, Z. Zahid, M. Tauqeer, C.-H. Park, J.P. Park, C.-H. Choi, T. Yoon, A.
 1743 Mohammad, State-of-the-art developments in metal/metal oxide and graphene-based
 1744 nano-hybrid systems for photocatalytic degradation of tetracycline antibiotics, *Journal*
 1745 *of Industrial and Engineering Chemistry* (2025).
- 1746 [161] A. Meera, M. Mahalakshmi, B. Neppolian, The strategy on selecting the
 1747 oxidation photocatalyst NiWO₄ as a co-catalyst to enhance the performance of
 1748 TiO₂/rGO for H₂ production under solar light, *International Journal of Hydrogen*
 1749 *Energy* 144 (2025) 186.
- 1750 [162] P.-Q. Wang, Y. Bai, P.-Y. Luo, J.-Y. Liu, Graphene-WO₃ nanobelt composite:
 1751 Elevated conduction band toward photocatalytic reduction of CO₂ into hydrocarbon
 1752 fuels, *Catalysis Communications* 38 (2013) 82.
 1753 <https://doi.org/10.1016/j.catcom.2013.04.020>
- 1754 [163] Y. Xia, B. Cheng, J. Fan, J. Yu, G. Liu, Near-infrared absorbing 2D/3D
 1755 ZnIn₂S₄/N-doped graphene photocatalyst for highly efficient CO₂ capture and
 1756 photocatalytic reduction, *Science China Materials* 63 (2020) 552.
 1757 <https://doi.org/10.1007/s40843-019-1234-x>
- 1758 [164] W.-J. Ong, L.-L. Tan, S.-P. Chai, S.-T. Yong, Graphene oxide as a structure-
 1759 directing agent for the two-dimensional interface engineering of sandwich-like
 1760 graphene-g-C₃N₄ hybrid nanostructures with enhanced visible-light photoreduction
 1761 of CO₂ to methane, *Chemical Communications* 51 (2015) 858.
 1762 <https://doi.org/10.1039/C4CC08996K>
- 1763 [165] H.-C. Hsu *et al.*, Graphene oxide as a promising photocatalyst for CO₂ to
 1764 methanol conversion, *Nanoscale* 5 (2013) 262. <https://doi.org/10.1039/C2NR31718D>




- [166] I. Shown *et al.*, Highly Efficient Visible Light Photocatalytic Reduction of CO₂ to Hydrocarbon Fuels by Cu-Nanoparticle Decorated Graphene Oxide, *Nano Letters* 14 (2014) 6097. <https://doi.org/10.1021/nl503609v>
- [167] J. Cheng, M. Zhang, G. Wu, X. Wang, J. Zhou, K. Cen, Photoelectrocatalytic Reduction of CO₂ into Chemicals Using Pt-Modified Reduced Graphene Oxide Combined with Pt-Modified TiO₂ Nanotubes, *Environmental Science & Technology* 48 (2014) 7076. <https://doi.org/10.1021/es500364g>
- [168] L.M. Pastrana-Martínez, A.M.T. Silva, N.N.C. Fonseca, J.R. Vaz, J.L. Figueiredo, J.L. Faria, Photocatalytic Reduction of CO₂ with Water into Methanol and Ethanol Using Graphene Derivative-TiO₂ Composites: Effect of pH and Copper(I) Oxide, *Topics in Catalysis* 59 (2016) 1279. <https://doi.org/10.1007/s11244-016-0655-2>
- [169] L.-L. Tan, W.-J. Ong, S.-P. Chai, A.R. Mohamed, Noble metal modified reduced graphene oxide/TiO₂ ternary nanostructures for efficient visible-light-driven photoreduction of carbon dioxide into methane, *Applied Catalysis B: Environmental* 166-167 (2015) 251. <https://doi.org/10.1016/j.apcatb.2014.11.035>
- [170] Z. Xiong, Y. Luo, Y. Zhao, J. Zhang, C. Zheng, J.C.S. Wu, Synthesis, characterization and enhanced photocatalytic CO₂ reduction activity of graphene supported TiO₂ nanocrystals with coexposed {001} and {101} facets, *Physical Chemistry Chemical Physics* 18 (2016) 13186. <https://doi.org/10.1039/C5CP07854G>
- [171] R. Gusain, P. Kumar, O.P. Sharma, S.L. Jain, O.P. Khatri, Reduced graphene oxide-CuO nanocomposites for photocatalytic conversion of CO₂ into methanol under visible light irradiation, *Applied Catalysis B: Environmental* 181 (2016) 352. <https://doi.org/10.1016/j.apcatb.2015.08.012>
- [172] L.-L. Tan, W.-J. Ong, S.-P. Chai, A.R. Mohamed, Photocatalytic reduction of CO₂ with H₂O over graphene oxide-supported oxygen-rich TiO₂ hybrid photocatalyst under visible light irradiation: Process and kinetic studies, *Chemical Engineering Journal* 308 (2017) 248. <https://doi.org/10.1016/j.cej.2016.09.050>
- [173] Q. Zhang, L. Huang, S. Kang, C. Yin, Z. Ma, L. Cui, Y. Wang, CuO/Cu₂O nanowire arrays grafted by reduced graphene oxide: synthesis, characterization, and application in photocatalytic reduction of CO₂, *RSC Advances* 7 (2017) 43642. <https://doi.org/10.1039/C7RA07310K>




- [174] S. Sorcar, J. Thompson, Y. Hwang, Y.H. Park, T. Majima, C.A. Grimes, J.K. Durrant, S.-I. In, High-rate solar-light photoconversion of CO₂ to fuel: controllable transformation from C₁ to C₂ products, *Energy & Environmental Science* 11 (2018) 3183. <https://doi.org/10.1039/C8EE00983J>
- [175] S. Kumar, R.K. Yadav, K. Ram, A. Aguiar, J. Koh, A.J.F.N. Sobral, Graphene oxide modified cobalt metallated porphyrin photocatalyst for conversion of formic acid from carbon dioxide, *Journal of CO₂ Utilization* 27 (2018) 107. <https://doi.org/https://doi.org/10.1016/j.jcou.2018.07.008>
- [176] P. Devi, J.P. Singh, Visible light induced selective photocatalytic reduction of CO₂ to CH₄ on In₂O₃-rGO nanocomposites, *Journal of CO₂ Utilization* 43 (2021) 101376. <https://doi.org/https://doi.org/10.1016/j.jcou.2020.101376>
- [177] X. Wang, Q. Li, C. Zhou, Z. Cao, R. Zhang, ZnO rod/reduced graphene oxide sensitized by α -Fe₂O₃ nanoparticles for effective visible-light photoreduction of CO₂, *Journal of Colloid and Interface Science* 554 (2019) 335. <https://doi.org/https://doi.org/10.1016/j.jcis.2019.07.014>
- [178] H.-T. Lien *et al.*, Solar to hydrocarbon production using metal-free water-soluble bulk heterojunction of conducting polymer nanoparticle and graphene oxide, *The Journal of Chemical Physics* 154 (2021) 164707. <https://doi.org/10.1063/5.0042716>
- [179] T. Wu, C. Zhu, D. Han, Z. Kang, L. Niu, Highly selective conversion of CO₂ to C₂H₆ on graphene modified chlorophyll Cu through multi-electron process for artificial photosynthesis, *Nanoscale* 11 (2019) 22980. <https://doi.org/10.1039/C9NR07824J>
- [180] K.M. Kamal *et al.*, Synergistic enhancement of photocatalytic CO₂ reduction by plasmonic Au nanoparticles on TiO₂ decorated N-graphene heterostructure catalyst for high selectivity methane production, *Applied Catalysis B: Environment and Energy* 307 (2022) 121181. <https://doi.org/https://doi.org/10.1016/j.apcatb.2022.121181>
- [181] H.R. Park, A.U. Pawar, U. Pal, T. Zhang, Y.S. Kang, Enhanced solar photoreduction of CO₂ to liquid fuel over rGO grafted NiO-CeO₂ heterostructure nanocomposite, *Nano Energy* 79 (2021) 105483. <https://doi.org/https://doi.org/10.1016/j.nanoen.2020.105483>




- [182] W. Tu *et al.*, Robust Hollow Spheres Consisting of Alternating Titania Nanosheets and Graphene Nanosheets with High Photocatalytic Activity for CO₂ Conversion into Renewable Fuels, *Advanced Functional Materials* 22 (2012) 1215. <https://doi.org/10.1002/adfm.201102566>
- [183] N. Nandal, P.K. Prajapati, B.M. Abraham, S.L. Jain, CO₂ to ethanol: A selective photoelectrochemical conversion using a ternary composite consisting of graphene oxide/copper oxide and a copper-based metal-organic framework, *Electrochimica Acta* 404 (2022) 139612. <https://doi.org/10.1016/j.electacta.2021.139612>
- [184] J. Yu, J. Jin, B. Cheng, M. Jaroniec, A noble metal-free reduced graphene oxide-CdS nanorod composite for the enhanced visible-light photocatalytic reduction of CO₂ to solar fuel, *Journal of Materials Chemistry A* 2 (2014) 3407. <https://doi.org/10.1039/C3TA14493C>
- [185] Y.T. Liang, B.K. Vijayan, O. Lyandres, K.A. Gray, M.C. Hersam, Effect of Dimensionality on the Photocatalytic Behavior of Carbon-Titania Nanosheet Composites: Charge Transfer at Nanomaterial Interfaces, *The Journal of Physical Chemistry Letters* 3 (2012) 1760. <https://doi.org/10.1021/jz300491s>
- [186] W. Tu, Y. Zhou, Q. Liu, S. Yan, S. Bao, X. Wang, M. Xiao, Z. Zou, An In Situ Simultaneous Reduction-Hydrolysis Technique for Fabrication of TiO₂-Graphene 2D Sandwich-Like Hybrid Nanosheets: Graphene-Promoted Selectivity of Photocatalytic-Driven Hydrogenation and Coupling of CO₂ into Methane and Ethane, *Advanced Functional Materials* 23 (2013) 1743. <https://doi.org/10.1002/adfm.201202349>
- [187] S. Liu, B. Weng, Z.-R. Tang, Y.-J. Xu, Constructing one-dimensional silver nanowire-doped reduced graphene oxide integrated with CdS nanowire network hybrid structures toward artificial photosynthesis, *Nanoscale* 7 (2015) 861. <https://doi.org/10.1039/C4NR04229H>
- [188] J. Hou, H. Cheng, O. Takeda, H. Zhu, Three-Dimensional Bimetal-Graphene-Semiconductor Coaxial Nanowire Arrays to Harness Charge Flow for the Photochemical Reduction of Carbon Dioxide, *Angewandte Chemie International Edition* 54 (2015) 8480. <https://doi.org/10.1002/anie.201502319>



- [189] X. An, K. Li, J. Tang, Cu₂O/Reduced Graphene Oxide Composites for the Photocatalytic Conversion of CO₂, *ChemSusChem* 7 (2014) 1086. <https://doi.org/https://doi.org/10.1002/cssc.201301194>
- [190] X. Li, Q. Wang, Y. Zhao, W. Wu, J. Chen, H. Meng, Green synthesis and photocatalytic performances for ZnO-reduced graphene oxide nanocomposites, *Journal of Colloid and Interface Science* 411 (2013) 69. <https://doi.org/https://doi.org/10.1016/j.jcis.2013.08.050>
- [191] P. Li, Y. Zhou, H. Li, Q. Xu, X. Meng, X. Wang, M. Xiao, Z. Zou, All-solid-state Z-scheme system arrays of Fe₂V₄O₁₃/RGO/CdS for visible light-driving photocatalytic CO₂ reduction into renewable hydrocarbon fuel, *Chemical Communications* 51 (2015) 800. <https://doi.org/10.1039/C4CC08744E>
- [192] J. Park, T. Jin, C. Liu, G. Li, M. Yan, Three-Dimensional Graphene-TiO₂ Nanocomposite Photocatalyst Synthesized by Covalent Attachment, *ACS Omega* 1 (2016) 351. <https://doi.org/10.1021/acsomega.6b00113>
- [193] M. Song *et al.*, Facile synthesis of MOF-808/RGO-based 3D macroscopic aerogel for enhanced photoreduction CO₂, *Journal of Colloid and Interface Science* 668 (2024) 471. <https://doi.org/https://doi.org/10.1016/j.jcis.2024.04.195>
- [194] J. Zhang, S. Shao, D. Zhou, Q. Xu, T. Wang, ZnO nanowire arrays decorated 3D N-doped reduced graphene oxide nanotube framework for enhanced photocatalytic CO₂ reduction performance, *Journal of CO₂ Utilization* 50 (2021) 101584. <https://doi.org/https://doi.org/10.1016/j.jcou.2021.101584>
- [195] Y.T. Liang, B.K. Vijayan, K.A. Gray, M.C. Hersam, Minimizing Graphene Defects Enhances Titania Nanocomposite-Based Photocatalytic Reduction of CO₂ for Improved Solar Fuel Production, *Nano Letters* 11 (2011) 2865. <https://doi.org/10.1021/nl2012906>
- [196] B. Kaur *et al.*, Catalytic performance of Graphdiyne for CO₂ reduction and charge dynamics progress, *Journal of Environmental Chemical Engineering* (2025) 116904.
- [197] F.-Y. Liu, H.-L. Chen, K.-Y. Hsiao, Y.-M. Dai, C.-C. Chen, I.-C. Chen, Unveiling photochemical CO₂ reduction processes on PbBiO₂I/GO surfaces: Insights from in-




- 1888 situ Raman spectroscopy, *Applied Catalysis B: Environment and Energy* 364 (2025) 124844.
- 1889
- 1890 [198] Z. Zhang, L. Li, S. Gao, P. Yang, Graphene interface modification to improve
- 1891 efficiency and stability at MAPbI₃/ZnO interface for perovskite solar cells: A first-
- 1892 principles study, *Solar Energy* 287 (2025) 113236.
- 1893 [199] U.U. Rehman, R.S. Almufarij, A. Abd-Elwahed, K.U. Sahar, E. Hussain, A.
- 1894 Ashfaq, K. Mahmood, C.-M. Wang, Improving efficiency of germanium-based
- 1895 perovskite solar cells with graphene interface layer: a strategy to minimize charge
- 1896 recombination, *Journal of Physics and Chemistry of Solids* 198 (2025) 112487.
- 1897 [200] S. Fu, H. Zhang, K.-J. Tielrooij, M. Bonn, H.I. Wang, Tracking and controlling
- 1898 ultrafast charge and energy flow in graphene-semiconductor heterostructures, *The*
- 1899 *Innovation* 6 (2025).
- 1900 [201] X. Zhou *et al.*, Weakness-complementing Z-scheme black phosphorus/TiO₂
- 1901 heterojunction with efficient charge separation and photocatalytic overall water
- 1902 splitting activity, *Journal of Colloid and Interface Science* 689 (2025) 137240.
- 1903 [202] A. Kamboukos, N. Todorova, I. Yarovsky, Exploring 2D Graphene-Based
- 1904 Nanomaterials for Biomedical Applications: A Theoretical Modeling Perspective,
- 1905 *Small Science* (2025) 2400505.
- 1906 [203] S. Samajdar, M. Biswas, D. Sarkar, J. Pramanik, J. Mukhopadhyay, S. Ghosh,
- 1907 Double heterojunction photocatalysts: strategic fabrication and mechanistic insights
- 1908 towards sustainable fuel production, *Chemical Communications* 61 (2025) 6069.
- 1909 [204] X. Zhu, Y. Hu, G. Wu, W. Chen, N. Bao, Two-dimensional nanosheets-based soft
- 1910 electro-chemo-mechanical actuators: recent advances in design, construction, and
- 1911 applications, *ACS nano* 15 (2021) 9273.
- 1912 [205] X. Lan, N. Luo, Z. Li, J. Peng, H.-M. Cheng, Status and prospect of two-
- 1913 dimensional materials in electrolytes for all-solid-state lithium batteries, *ACS nano* 18
- 1914 (2024) 9285.
- 1915 [206] Z. Zhou, W. Qi, Z. Li, L. Yang, Z. Lin, R. Guan, N-P Type Charge Compensatory
- 1916 Synergistic Effect for Schottky and Efficient Photoelectrocatalysis Applications:
- 1917 Doping Mechanism in (Nb/Re)@ WS₂/Graphene Heterojunctions, *Chemistry-A*
- 1918 *European Journal* 31 (2025) e202403963.




- 1919 [207] F. Gomes *et al.*, Advancing Dye-Sensitized Solar Cells: Synergistic Effects of
 1920 Polyaniline, Graphene Oxide, and Carbon Nanotubes for Enhanced Efficiency and
 1921 Sustainability Developments, Recent patents on nanotechnology (2025).
- 1922 [208] D. Das, M. Das, S. Sil, P. Sahu, P.P. Ray, Effect of Higher Carrier Mobility of the
 1923 Reduced Graphene Oxide–Zinc Telluride Nanocomposite on Efficient Charge
 1924 Transfer Facility and the Photodecomposition of Rhodamine B, ACS Omega 7 (2022)
 1925 26483. <https://doi.org/10.1021/acsomega.2c02472>
- 1926 [209] G.S. Natarajamani, V.P. Kannan, S. Madanagurusamy, Synergistic ramifications
 1927 of a sustainable ultra-sensitive NH₃ sensor: Thermally reduced graphene oxide/ZnO
 1928 hybrid composite for sub-PPM detection, Journal of Environmental Chemical
 1929 Engineering 13 (2025) 116079.
- 1930 [210] T. Sewela, R. Ocaya, T. Malevu, Recent insights into the transformative role of
 1931 Graphene-based/TiO₂ electron transport layers for perovskite solar cells, Energy
 1932 Science & Engineering 13 (2025) 4.
- 1933 [211] F. Ullah, B.H. Guan, M. Zafar, N. e Hira, H. Khan, M.S.M. Saheed, Synergistic
 1934 enhancement in PEC hydrogen production using novel GQDs and CuO modified
 1935 TiO₂ based heterostructure photocatalyst, Materials Chemistry and Physics 340 (2025)
 1936 130781.
- 1937 [212] D. Maarisetty, R. Mary, D.-R. Hang, P. Mohapatra, S.S. Baral, The role of material
 1938 defects in the photocatalytic CO₂ reduction: Interfacial properties, thermodynamics,
 1939 kinetics and mechanism, Journal of CO₂ Utilization 64 (2022) 102175.
- 1940 [213] C.A. Celaya, C. Delesma, P. Valadés-Pelayo, O.A. Jaramillo-Quintero, C.O.
 1941 Castillo-Araiza, L. Ramos, P. Sebastian, J. Muñiz, Exploring the potential of graphene
 1942 oxide as a functional material to produce hydrocarbons via photocatalysis: Theory
 1943 meets experiment, Fuel 271 (2020) 117616.
- 1944 [214] M.Y. Akram, T. Ashraf, M.S. Jagirani, A. Nazir, M. Saqib, M. Imran, Recent
 1945 advances in graphene-based single-atom photocatalysts for CO₂ reduction and H₂
 1946 production, Catalysts 14 (2024) 343.
- 1947 [215] J.O. Olowoyo, M. Kumar, B. Singh, V.O. Oninla, J.O. Babalola, H. Valdés, A.V.
 1948 Vorontsov, U. Kumar, Self-assembled reduced graphene oxide-TiO₂ nanocomposites:




- 1949 Synthesis, DFTB+ calculations, and enhanced photocatalytic reduction of CO₂ to
 1950 methanol, Carbon 147 (2019) 385.
- 1951 [216] Y. Cui, X. Huang, T. Wang, L. Jia, Q. Nie, Z. Tan, H. Yu, Graphene quantum
 1952 dots/carbon nitride heterojunction with enhanced visible-light driven photocatalysis
 1953 of nitric oxide: An experimental and DFT study, Carbon 191 (2022) 502.
- 1954 [217] A. Olatomiwa, T. Adam, C. Edet, A. Adewale, A. Chik, M. Mohammed, S.C.
 1955 Gopinath, U. Hashim, Recent advances in density functional theory approach for
 1956 optoelectronics properties of graphene, Heliyon 9 (2023).
- 1957 [218] M. Khenfouch, M. Baïtoul, M. Maaza, White photoluminescence from a grown
 1958 ZnO nanorods/graphene hybrid nanostructure, optical Materials 34 (2012) 1320.
- 1959 [219] B. Weng, Y.-J. Xu, What if the electrical conductivity of graphene is significantly
 1960 deteriorated for the graphene–semiconductor composite-based photocatalysis?, ACS
 1961 Applied Materials & Interfaces 7 (2015) 27948.
- 1962 [220] Y. Xiang, L. Xin, J. Hu, C. Li, J. Qi, Y. Hou, X. Wei, Advances in the applications
 1963 of graphene-based nanocomposites in clean energy materials, Crystals 11 (2021) 47.
- 1964 [221] G. Marineau-Plante *et al.*, Effect of mesogenic side groups on the redox,
 1965 photophysical, and solar cell properties of diketopyrrolopyrrole-trans-bis
 1966 (diphosphine) diethynylplatinum (II) polymers, ACS Applied Polymer Materials 3
 1967 (2021) 1087.
- 1968 [222] H. Kasap, 2019.
- 1969 [223] A.G. Al-Gamal, A.M. Elseman, K.I. Kabel, Advances in Nitrogen-Functionalized
 1970 Graphene for Enhanced Photovoltaic Applications, Solar RRL 9 (2025) 2500002.
- 1971 [224] E. Flórez, C. Jimenez-Orozco, N. Acelas, Unravelling the influence of surface
 1972 functional groups and surface charge on heavy metal adsorption onto carbonaceous
 1973 materials: an in-depth DFT study, Materials Today Communications 39 (2024) 108647.
- 1974 [225] M. Yang, B. Qin, C. Si, X. Sun, B. Li, Electrochemical reactions catalyzed by
 1975 carbon dots from computational investigations: functional groups, dopants, and
 1976 defects, Journal of Materials Chemistry A 12 (2024) 2520.
- 1977 [226] Y. Li, W. Niu, T. Chen, Y. Sun, M. Yu, Integrating vacancy engineering and
 1978 energy-level adapted coupling of electrocatalyst for enhancement of carbon dioxide
 1979 conversion, Applied Catalysis B: Environmental 321 (2023) 122037.




- [227] S. Xu, E.A. Carter, CO₂ photoelectrochemical reduction catalyzed by a GaP (001) photoelectrode, *ACS Catalysis* 11 (2021) 1233.
- [228] X. Xu, C. Liu, Z. Sun, T. Cao, Z. Zhang, E. Wang, Z. Liu, K. Liu, Interfacial engineering in graphene bandgap, *Chemical Society Reviews* 47 (2018) 3059.
- [229] S. Nakaharai, T. Iijima, S. Ogawa, S. Suzuki, S.-L. Li, K. Tsukagoshi, S. Sato, N. Yokoyama, Conduction tuning of graphene based on defect-induced localization, *ACS nano* 7 (2013) 5694.
- [230] M. Kumar Kumawat, S. Kumar, T. Mohanty, Tailoring functional properties of graphene oxide by defect-assisted surface and interface modifications, *Journal of Materials Research* 37 (2022) 3394.
- [231] I. Shtepliuk, Defect-induced modulation of a 2D ZnO/graphene heterostructure: exploring structural and electronic transformations, *Applied Sciences* 13 (2023) 7243.
- [232] K.P. Dhakal *et al.*, Local strain induced band gap modulation and photoluminescence enhancement of multilayer transition metal dichalcogenides, *Chemistry of Materials* 29 (2017) 5124.
- [233] D. Maarisetty, S.S. Baral, Defect engineering in photocatalysis: formation, chemistry, optoelectronics, and interface studies, *Journal of Materials Chemistry A* 8 (2020) 18560.
- [234] M. Shen, L. Zhang, J. Shi, Defect engineering of photocatalysts towards elevated CO₂ reduction performance, *ChemSusChem* 14 (2021) 2635.
- [235] B. Wang, G. Du, S. Tan, S. Guo, Z. Zhu, G.-F. Huang, W.-Q. Huang, R. Jiang, Constructing a Double Type-II G-C₃N₄/CdS/MoS₂ (GCSM) Heterojunction with Dual-Enhanced Redox Capability for Efficient Photocatalytic Pollutant Degradation, Shengxia and Guo, Shengwei and Zhu, ZhongHua and Huang, Gui-Fang and Huang, Wei-Qing and Jiang, Ru, Constructing a Double Type-II G-C₃N₄/CdS/MoS₂ (GCSM) Heterojunction with Dual-Enhanced Redox Capability for Efficient Photocatalytic Pollutant Degradation.
- [236] S. Zhang, X. Zhang, W. Shi, H. Weiyan, X. Wang, The Study on the Construction of S-Scheme G-C₃N₄/Mof Heterojunctions Through Interface and Built-In Electric Field Modulation and Their Photocatalytic Degradation Performance of Tetracycline, Xiaojing, The Study on the Construction of S-Scheme G-C₃N₄/Mof Heterojunctions




- 2011 Through Interface and Built-In Electric Field Modulation and Their Photocatalytic
 2012 Degradation Performance of Tetracycline.
- 2013 [237] Y. Wang, Y. Liu, H. Zhang, X. Duan, J. Ma, H. Sun, W. Tian, S. Wang,
 2014 Carbonaceous materials in structural dimensions for advanced oxidation processes,
 2015 Chemical Society Reviews (2025).
- 2016 [238] Q. Tian, Q. Li, T. Zhang, W. Huang, C. Zhao, B. Hu, X. Xu, Molecular Orbital
 2017 Level Micro-Electric Field in Green Fenton-Like Chemistry for Water Treatment: From
 2018 Mechanism Understanding to Scale-Up Applications, Advanced Materials (2025)
 2019 e09280.
- 2020 [239] N.N. Rabin, H. Ohmagari, M.S. Islam, M.R. Karim, S. Hayami, A procession on
 2021 photocatalyst for solar fuel production and waste treatment, Journal of Inclusion
 2022 Phenomena and Macrocyclic Chemistry 94 (2019) 263.
- 2023 [240] M.D. Ali, A. Starczewska, T.K. Das, M. Jesionek, Exploration of Sp-Sp² Carbon
 2024 Networks: Advances in Graphyne Research and Its Role in Next-Generation
 2025 Technologies, International Journal of Molecular Sciences 26 (2025) 5140.
- 2026 [241] F. Liu, G. Wei, B. Hu, A review on n-type chemical doping of graphene films:
 2027 preparation, characterization and applications, Nanoscale (2025).
- 2028 [242] L.K. Putri, W.-J. Ong, W.S. Chang, S.-P. Chai, Heteroatom doped graphene in
 2029 photocatalysis: A review, Applied Surface Science 358 (2015) 2.
 2030 <https://doi.org/https://doi.org/10.1016/j.apsusc.2015.08.177>
- 2031 [243] J. Jianga, Y. Zhanga, W. Suna, J. Penga, W. Shib, Y. Quc, E. Liud, A review of
 2032 updated red phosphorus-based photocatalysts, (2025).
- 2033 [244] W. Zhu, B. Zhang, Y. Yang, M. Zhao, Y. Fang, Y. Cui, J. Tian, Enhanced
 2034 Electrocatalytic Performance of P-Doped MoS₂/rGO Composites for Hydrogen
 2035 Evolution Reactions, Molecules 30 (2025) 1205.
- 2036 [245] S. Zhi, Q. Dai, H. Wang, D. Wu, L. Zhao, C. Hu, L. Dai, Heteroatom-Doped
 2037 Carbon Materials for Multifunctional Noncatalytic Applications, ACS nano (2025).
- 2038 [246] H. Noorizadeh, R.H. Al Omari, A. Kumar, A.F. Al-Hussainy, S. Mohammed, A.
 2039 Sinha, S. Ray, Indium Phosphide Quantum Dots as Green Nanosystems for
 2040 Environmental Detoxification: Surface Engineering, Photocatalytic Mechanisms, and
 2041 Comparative Material Insights, Environmental Science: Advances (2025).




- 2042 [247] Z.A. Sandhu, U. Farwa, M. Danish, M.A. Raza, A. Talib, H. Amjad, R. Riaz, A.G.
 2043 Al-Sehemi, Sustainability and photocatalytic performance of MOFs: Synthesis
 2044 strategies and structural insights, *Journal of Cleaner Production* (2024) 143263.
 2045 [248] D.S. Constantino, M.M. Dias, A.M. Silva, J.L. Faria, C.G. Silva, Intensification
 2046 strategies for improving the performance of photocatalytic processes: A review,
 2047 *Journal of Cleaner Production* 340 (2022) 130800.
 2048 [249] S. Sadana, N. Rajamohan, R. Manivasagan, N. Raut, S. Paramasivam, G. Gatto,
 2049 A. Kumar, Graphene-based materials for photocatalytic and environmental sensing
 2050 applications, *RESULTS IN ENGINEERING* 27 (2025).
 2051 [250] I. Razzaq *et al.*, Graphene-Based Polymer Composites for High-Performance
 2052 Chemical Sensing and Detection: A Critical Review, *Advanced Materials*
 2053 *Technologies* e00578.
 2054 [251] R. Atchudan, T.N.J.I. Edison, S. Perumal, D. Karthikeyan, Y.R. Lee, Facile
 2055 synthesis of zinc oxide nanoparticles decorated graphene oxide composite via simple
 2056 solvothermal route and their photocatalytic activity on methylene blue degradation,
 2057 *Journal of Photochemistry and Photobiology B: Biology* 162 (2016) 500.
 2058 [252] M. Ahmad, E. Ahmed, Z. Hong, N. Khalid, W. Ahmed, A. Elhissi, Graphene-
 2059 Ag/ZnO nanocomposites as high performance photocatalysts under visible light
 2060 irradiation, *Journal of alloys and compounds* 577 (2013) 717.
 2061 [253] X. Liu, A. Hu, Z. Liu, K. Ding, W. Xia, H. Shangguan, C. Zhang, T. Fu, Review
 2062 on fundamental and recent advances of strain engineering for enhancing
 2063 photocatalytic CO₂ reduction, *Advanced Energy Materials* 15 (2025) 2405320.
 2064 [254] L.T. Mambiri, University of Louisiana at Lafayette, 2025.
 2065 [255] L. Jiang, X. Zhi, X. Bai, Y. Jiao, Atomic-level insights into cation-mediated
 2066 mechanism in electrochemical nitrogen reduction, *Journal of the American Chemical*
 2067 *Society* 147 (2025) 16935.
 2068 [256] G.G. Nezhad, H. Esfandian, M.S. Lashkenari, Synthesis and Electrocatalytic
 2069 Performance of Cu-Pb/RGO Composite for Efficient CO₂ Reduction to Methanol,
 2070 *Results in Engineering* (2025) 105436.




- 2071 [257] S.J. Armaković, S. Armaković, A. Bilić, M.M. Savanović, **ZnO-Based** View Article Online
DOI: 10.1039/D5MA00750J
2072 Photocatalysts: Synergistic Effects of Material Modifications and Machine Learning
2073 Optimization, *Catalysts* 15 (2025) 793.
- 2074 [258] Q. Adfar, S. Hussain, S.S. Maktedar, Insights into energy and environmental
2075 sustainability through photoactive graphene-based advanced materials: perspectives
2076 and promises, *New Journal of Chemistry* (2025).
- 2077 [259] S. Sambyal, P. Raizada, A. Chawla, A.A.P. Khan, S. Thakur, V.-H. Nguyen, P.
2078 Singh, Tuning ZnCdS heterostructures for enhanced photocatalysis: hybrid
2079 architectures for sustainable energy and environmental applications, *Journal of*
2080 *Materials Chemistry A* (2025).
- 2081 [260] G.I. Edo *et al.*, Green Biosynthesis of Nanoparticles Using Plant Extracts:
2082 Mechanisms, Advances, Challenges, and Applications, *BioNanoScience* 15 (2025) 267.
- 2083 [261] V. Jayant, R. Kumar, P. Tyagi, M. Yusuf, *Green Chemistry*, Elsevier, 2025, p. 67-
2084 96.
- 2085 [262] G.B. Mahendran, S.J. Ramalingam, J.B.B. Rayappan, S. Kesavan, T. Periathambi,
2086 N. Nesakumar, Green preparation of reduced graphene oxide by *Bougainvillea glabra*
2087 flower extract and sensing application, *Journal of Materials Science: Materials in*
2088 *Electronics* 31 (2020) 14345. <https://doi.org/10.1007/s10854-020-03994-4>
- 2089 [263] J. Singh, D.D. Nguyen, P. Leclerc, P. Nguyen-Tri, Recent Advancements in
2090 Graphene-Based Nanocomposites for Enhanced Photocatalysis in Environmental
2091 Remediation: A Comprehensive Review, *Reviews of Environmental Contamination*
2092 *and Toxicology* 263 (2025) 13.
- 2093 [264] P. Rana, P. Singh, V. Puri, Q. Van Le, T. Ahamad, T.T. Le, V.-H. Nguyen, P.
2094 Raizada, Flat meets functional: face-to-face 2D/2D S-scheme photocatalysts for
2095 efficient CO₂-to-fuel conversion, *Sustainable Energy & Fuels* (2025).
- 2096 [265] S.H. Osman, S.K. Kamarudin, M.H. Jamil, E. Alfianto, N. Shaari, Z. Zakaria, 3D
2097 Graphene-Coupled Aerogel Nanoarchitectures: Emerging Paradigm Toward
2098 Sustainable Applications in Fuel Cell, *Korean Journal of Chemical Engineering* (2025)
2099 1.
- 2100 [266] H. Ali *et al.*, Defect-driven innovations in photocatalysts: Pathways to enhanced
2101 photocatalytic applications, *InfoMat* e70040.



- [267] S.H. Emon, M.I. Hossain, M. Khanam, D.K. Yi, Expanding Horizons: Taking Advantage of Graphene's Surface Area for Advanced Applications, (2025).
- [268] L. Ma *et al.*, Metal organic frameworks for photocatalytic CO₂ reduction to CO with high selectivity: Mechanism and strategy, Nano Research (2025).
- [269] J. Yu, G. Wang, B. Cheng, M. Zhou, Effects of hydrothermal temperature and time on the photocatalytic activity and microstructures of bimodal mesoporous TiO₂ powders, Applied Catalysis B: Environmental 69 (2007) 171. <https://doi.org/https://doi.org/10.1016/j.apcatb.2006.06.022>
- [270] M. Tang, Y. Xia, D. Yang, J. Liu, X. Zhu, R. Tang, Effects of hydrothermal time on structure and photocatalytic property of titanium dioxide for degradation of rhodamine b and tetracycline hydrochloride, Materials 14 (2021) 5674.
- [271] T.T.P.N.X. Trinh *et al.*, Hydrothermal synthesis of titanium dioxide/graphene aerogel for photodegradation of methylene blue in aqueous solution, Journal of Science: Advanced Materials and Devices 7 (2022) 100433. <https://doi.org/https://doi.org/10.1016/j.jsamd.2022.100433>
- [272] A.a. Zhou, J. Bai, W. Hong, H. Bai, Electrochemically reduced graphene oxide: Preparation, composites, and applications, Carbon 191 (2022) 301. <https://doi.org/https://doi.org/10.1016/j.carbon.2022.01.056>
- [273] A.G. Marrani, A. Motta, F. Amato, R. Schrebler, R. Zanoni, E.A. Dalchiele, Effect of electrolytic medium on the electrochemical reduction of graphene oxide on Si (111) as probed by XPS, Nanomaterials 12 (2021) 43.
- [274] R.Y.N. Gengler, D.S. Badali, D. Zhang, K. Dimos, K. Spyrou, D. Gournis, R.J.D. Miller, Revealing the ultrafast process behind the photoreduction of graphene oxide, Nature Communications 4 (2013) 2560. <https://doi.org/10.1038/ncomms3560>
- [275] H.W. Cho, J.J. Wu, Photoreduction of graphene oxide enhanced by sacrificial agents, J Colloid Interface Sci 438 (2015) 291. <https://doi.org/10.1016/j.jcis.2014.10.006>
- [276] H. Singh *et al.*, Revisiting the Green Synthesis of Nanoparticles: Uncovering Influences of Plant Extracts as Reducing Agents for Enhanced Synthesis Efficiency and Its Biomedical Applications, Int J Nanomedicine 18 (2023) 4727. <https://doi.org/10.2147/ijn.S419369>



- 2133 [277] Y. Wang, J. Yu, W. Xiao, Q. Li, Microwave-assisted hydrothermal synthesis of
2134 graphene based Au-TiO₂ photocatalysts for efficient visible-light hydrogen
2135 production, *Journal of Materials Chemistry A* 2 (2014) 3847.
- 2136 [278] P. Zhang, X. Teng, X. Feng, S. Ding, G. Zhang, Preparation of Bi₂WO₆
2137 photocatalyst by high-energy ball milled Bi₂O₃-WO₃ mixture, *Ceramics International*
2138 42 (2016) 16749. <https://doi.org/10.1016/j.ceramint.2016.07.148>
- 2139 [279] L. Zhang, L. Jin, B. Liu, J. He, Templated growth of crystalline mesoporous
2140 materials: from soft/hard templates to colloidal templates, *Frontiers in chemistry* 7
2141 (2019) 22.
- 2142 [280] R.J. Li, W.J. Niu, W.W. Zhao, B.X. Yu, C.Y. Cai, L.Y. Xu, F.M. Wang,
2143 Achievements and Challenges in Surfactants-Assisted Synthesis of MOFs-Derived
2144 Transition Metal-Nitrogen-Carbon as a Highly Efficient Electrocatalyst for ORR,
2145 OER, and HER, *Small* 21 (2025) 2408227.
- 2146 [281] Z. Tong, Y. Hai, B. Wang, F. Lv, Z. Zhong, R. Xiong, Activated g-C₃N₄
2147 Photocatalyst with Defect Engineering for Efficient Reduction of CO₂ in Water, *The*
2148 *Journal of Physical Chemistry C* 127 (2023) 11067.
2149 <https://doi.org/10.1021/acs.jpcc.3c02076>
- 2150 [282] M. Mehrpooya, F. Bayatlar, Photocatalytic Reactors for CO₂ Reduction: Review
2151 on Simulation Studies, *Archives of Computational Methods in Engineering* (2025) 1.
- 2152 [283] Z. Sun, X. He, L. Duan, Multifunctional Soft and Solid Materials for Integrated
2153 CO₂ Capture and Utilization: Prospects and Opportunities, *Advanced Functional*
2154 *Materials* (2025) e24549.
- 2155 [284] S. Chakraborty, S.C. Peter, Solar-Fuel Production by Photodriven CO₂
2156 Reduction: Facts, Challenges, and Recommendations, *ACS Energy Letters* 10 (2025)
2157 2359.
- 2158 [285] M. Zhan, M. Xu, W. Lin, H. He, C. He, Graphene Oxide Research: Current
2159 Developments and Future Directions, *Nanomaterials* 15 (2025) 507.
- 2160 [286] M. Ramezani, O. Rahmani, A review of recent progress in the graphene
2161 syntheses and its applications, *Mechanics of Advanced Materials and Structures*
2162 (2024) 1.



2163 [287] C. Amutha, A. Gopan, I. Pushbalatatha, M. Ragavi, J.A. Reneesse, *Nanotechnology in Societal Development*, Springer, 2024, p. 481-503. View Article Online
DOI: 10.1039/D3MA00750J

2164

2165 [288] H.-Y. Zhuo, X. Zhang, J.-X. Liang, Q. Yu, H. Xiao, J. Li, Theoretical

2166 understandings of graphene-based metal single-atom catalysts: stability and catalytic

2167 performance, *Chemical reviews* 120 (2020) 12315.

2168 [289] H. Chen, Y. Zheng, J. Li, L. Li, X. Wang, AI for nanomaterials development in

2169 clean energy and carbon capture, utilization and storage (CCUS), *ACS nano* 17 (2023)

2170 9763.

2171 [290] R. Awasthy, S. Flint, R. Sankarnarayana, R.L. Jones, A framework to improve

2172 university-industry collaboration, *Journal of Industry-University Collaboration* 2

2173 (2020) 49.

2174 [291] N. Kalaiselvan, T. Mathimani, Solar-driven green hydrogen generation for

2175 revolutionizing the future of zero-carbon energy, *Fuel* 375 (2024) 132538.

2176



No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

[View Article Online](#)
DOI: 10.1039/D5MA00750J

