



Cite this: *Nanoscale Horiz.*, 2025, 10, 2486

Received 17th April 2025,  
Accepted 21st July 2025

DOI: 10.1039/d5nh00254k

rsc.li/nanoscale-horizons

# Unraveling the $\text{Mn}^{2+}$ substitution effect on the anisotropy control and magnetic hyperthermia of $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$ nanoparticles†

Oscar F. Odio,<sup>a</sup> Giuseppina Tommasini,<sup>bh</sup> F. J. Teran,<sup>cd</sup> Jesus G. Ovejero,<sup>e</sup> Javier Rubin,<sup>f</sup> María Moros<sup>id</sup>\*<sup>bg</sup> and Susel Del Sol-Fernández<sup>id</sup>‡<sup>ab</sup>

Composition is a key parameter to effectively tune the magnetic anisotropy of magnetic nanoparticles, which in turn can modulate their structural–magnetic properties and final applications. The  $\text{Mn}^{2+}$  content of manganese ferrite nanoparticles ( $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$ ) deeply impacts their structure, anisotropy, magnetism, and their heating capacity. However, a direct correlation between  $\text{Mn}^{2+}$  content, magnetic properties and heating efficiency is not yet clear. Herein, we report the synthesis of a wide range of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  with  $x = 0.14$  to 1.40, with similar polyhedral morphologies and sizes (13 to 15 nm). By varying the  $\text{Mn}^{2+}$  content (in the range of  $x = 0.0$  up to 0.70), we successfully tuned the effective anisotropy while maintaining saturation magnetization nearly constant. Highest  $\text{Mn}^{2+}$  levels ( $x = 1.40$ ) lead to structural changes and strain defects reflected in their poor saturation magnetization.  $\text{Mn}^{2+}$  substitution is not uniform, instead promotes a

## New concepts

We present a successful strategy to tune the heating efficiency of manganese ferrite nanoparticles ( $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$ ) by systematically varying the  $\text{Mn}^{2+}$  content, while maintaining consistent the size and shape. This approach uncovers a direct correlation between the  $\text{Mn}^{2+}$  content, effective anisotropy, and heating performance – key parameters for optimizing magnetic hyperthermia agents. A key discovery is that  $\text{Mn}^{2+}$  incorporation is not uniform – it begins on the nanoparticle surface, creating a compositional gradient. This gradient leads to superparamagnetic relaxation on the Mn-rich surface and ferrimagnetic behavior in the core. We identify an optimal  $\text{Mn}^{2+}$  content ( $x \approx 0.60$ –0.70) that maximizes effective anisotropy and SLP, while preserving biocompatibility (> 90% cell viability after 24 h). In contrast, high  $\text{Mn}^{2+}$  levels ( $x \approx 1.40$ ) lead to structural defects,  $\text{Mn}^{3+}$  species, and reduced magnetization. Despite ion leaching during water transfer *via* PMAO coating, key magnetic properties are retained. This work provides critical new insight into how compositional control – independent of morphology and size – affects magnetic relaxation and heating performance, offering a rational framework for the design of stable, efficient, and safe magnetic nanoparticles for application in nanomedicine.

compositional gradient across the MNPs, with the surface layers having a higher concentration of  $\text{Mn}^{2+}$  than the core. The  $\text{Mn}^{2+}$ -rich surface likely exhibits superparamagnetic (SPM) relaxation, while the core remains predominantly ferrimagnetic (FiM). Water transference results in cation leaching, promoting vacancies and changes in the local ferrite structure but with a minor impact on the magnetic properties compared with initial MNPs. We obtained the optimal  $\text{Mn}^{2+}$  content that maximizes anisotropy toward improved specific loss power (SLP) values. The Néel relaxation mechanism is warranted regarding variable composition when sizes and shapes are maintained. Our detailed analysis provides a better understanding of the effect of  $\text{Mn}^{2+}$  substitution on the heating efficiency through anisotropy modulation and straightforward guidance on optimizing MNP design for magnetic hyperthermia.

## 1. Introduction

Manganese ferrite nanoparticles ( $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs) have attracted considerable attention for their potential applications

<sup>a</sup> SECIHTI-Instituto Politécnico Nacional, Laboratorio Nacional de Conversión y Almacenamiento de Energía, CICATA-Legaria, 11500 Mexico City, Mexico

<sup>b</sup> Instituto de Nanociencia y Materiales de Aragón, INMA (CSIC-Universidad de Zaragoza), C/ Pedro Cerbuna 12, 50009, Zaragoza, Spain.

E-mail: m.moros@csic.es

<sup>c</sup> iMdea Nanociencia, Campus Universitario de Cantoblanco, 28049 Madrid, Spain

<sup>d</sup> Unidad de Nanomateriales Avanzados, iMdea Nanociencia, Unidad Asociada al CSIC, Madrid, Spain

<sup>e</sup> Instituto de Ciencia de Materiales de Madrid, ICMM (CSIC), Sor Juana Inés de la Cruz 3, 28049 Madrid, Spain

<sup>f</sup> Dept. Materials Science and Metallurgy, Escuela de Ingeniería y Arquitectura (EINA), Universidad de Zaragoza, María de Luna 3, 50018 Zaragoza, Spain

<sup>g</sup> Centro de Investigación Biomédica en Red de Bioingeniería, Biomateriales y Nanomedicina (CIBER-BBN), Madrid, Spain

<sup>h</sup> Istituto di Scienze Applicate e Sistemi Intelligenti “E. Caianiello”, Consiglio Nazionale delle Ricerche, Via Campi Flegrei 34, Pozzuoli, 80078, Italy

† Electronic supplementary information (ESI) available: Experimental conditions employed for the synthesis of the two series of MNPs. TEM characterization of samples with equal compositions but varying ratios of OA/Fe-Mn, EDX spectra, lattice strain calculations, a section dedicated to curve fitting of the high-resolution spectra of Mn 3s and Fe 3s signals and proper quantification of Mn/Fe ratios, high resolution XPS spectra, TGA analysis, the magnetic properties of oleic acid coated MNPs at 300 K, heating curves under different frequencies, SAR evolution vs. glycerol content, and SAR values obtained from AC magnetometry. See DOI: <https://doi.org/10.1039/d5nh00254k>

‡ Present address: Instituto de Ciencias Físicas, Universidad Nacional Autónoma de México, Av. Universidad s/n, Col. Chamilpa, Cuernavaca, Morelos 62210, Mexico. E-mail: sdelsol@icf.unam.mx



in magnetic hyperthermia therapy (MHT) and magnetic resonance imaging (MRI).<sup>1</sup> The substitution of  $\text{Fe}^{2+}$  by  $\text{Mn}^{2+}$  in the spinel structure can significantly alter their magnetic anisotropy, saturation magnetization ( $M_s$ ), heating, and contrast efficiency due to changes in their structural properties, including crystal structure, crystallite size, and lattice parameter.<sup>2–4</sup> While the impact of the  $\text{Mn}^{2+}$  content on the magnetic properties has been investigated in recent years using many different  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs,<sup>5–8</sup> a direct correlation between the  $\text{Mn}^{2+}$  content and the magnetic properties is not yet clear. For instance, a broad range of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs ( $0 \leq x < 1$ ) prepared by the co-precipitation method showed a monotone increase of lattice parameters and heating capacity as the  $\text{Mn}^{2+}$  content increased, although these results could not be exclusively attributed to the  $\text{Mn}^{2+}$  content due to the size dispersion between samples.<sup>9</sup> Conversely, other authors did not find a correlation between  $\text{Mn}^{2+}$  content and magnetic properties of MNPs<sup>7,10,11</sup> or reported that the net  $M_s$  values did not consistently increase with  $\text{Mn}^{2+}$  content,<sup>12</sup> even when a correlation between crystallite size and  $\text{Mn}^{2+}$  content was observed. Most notably, while computational modelling revealed a positive correlation between the  $\text{Mn}^{2+}$  content and  $M_s$ ,<sup>13</sup> experimental data showed an opposite trend, which was attributed to a reduction in both the crystallite and magnetic diameters promoted by the incorporation of  $\text{Mn}^{2+}$ . Therefore, it is clear that one of the major challenges in studying how the composition of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs impacts on the structural-magnetic properties is maintaining similar average size, shape, and monodispersity across all samples, a fact that has been frequently overlooked.

These discrepancies across reports are also reflected in the optimal conditions for effective heat dissipation under an alternating magnetic field (AMF). For instance, similar specific loss power (SLP) under an AMF has been observed in samples with markedly different composition,<sup>14,15</sup> whereas samples with similar composition produced significant differences in terms of heat generation depending on their internal structural

defects.<sup>3</sup> The optimal  $\text{Mn}^{2+}$  content needed to efficiently dissipate heat under similar AMF conditions is not yet clear.<sup>4,16</sup>

Therefore, further studies are necessary to better understand how composition can affect all these properties. More importantly, in many cases, these studies are performed exclusively in organic solvents, overlooking the impact that the water transference protocols can have on the final composition and the magnetic properties, potentially leading to partial or misleading interpretations. Soriano *et al.* reported  $\text{Mn}^{2+}$  leaching, and consequently, composition changes after water transference by using meso-2,3-dimercaptosuccinic acid (DMSA) and dopamine (DOPA) ligands.<sup>16</sup> This leaching could alter the crystal structure of the MNPs, significantly affecting their magnetic properties.

In this work, we present a detailed and systematic study of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs ( $x_{\text{Empiric}} = 0.14\text{--}1.40$ ) with similar sizes and shapes, synthesized by a one-step thermal decomposition method, with the aim of investigating  $\text{Mn}^{2+}$  substitution effects on the structural, anisotropy, magnetic behaviour and heating properties of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs. To achieve this, we synthesized seven MNP samples by varying critical synthetic parameters, including the ratio of metallic precursors, final solvent volume, and the surfactant-to-metallic precursor ratio. A detailed investigation into the manganese oxidation state and allocation of cations among the samples revealed, for the first time, that the incorporation of manganese ions into the ferrite structure begins at the outermost layers and progressively extends toward the MNP core. We concluded that  $\text{Mn}^{2+}$  substitution is not uniform: instead, a concentration gradient is observed, with a higher  $\text{Mn}^{2+}$  fraction on the surface. The  $\text{Mn}^{2+}$ -rich surface dictated the preferential magnetic relaxation of the MNPs, as seen by Mössbauer spectroscopy. Finally, we investigated the impact of a polymer coating on the final compositions of the  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs, their crystal structure and magnetic properties. This work provides valuable insights into how tailoring  $\text{Mn}^{2+}$  content can be used to effectively tune anisotropy and heating efficiency, thus advancing the understanding and optimization of MHT.

## 2. Materials and methods

### 2.1. Materials

Iron(III) acetylacetonate ( $\text{Fe}(\text{acac})_3$ , 97%), manganese(II) acetylacetonate ( $\text{Mn}(\text{acac})_2$ , 98%), oleic acid (OA, 90%), 1,2-hexadecanediol (technical grade, 90%), dibenzyl ether (DBE, 90%), poly(maleic anhydride-*alt*-1-octadecene) (PMAO) (MW = 30 000–50 000 Da), *N*-(3-dimethylaminopropyl)-*N*-ethylcarbodiimide hydrochloride (EDC), 4-aminophenyl  $\beta$ -D-glucopyranoside and 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium (MTT) were purchased from Sigma-Aldrich. Tetramethylrhodamine 5-(and -6)-carboxamide cadaverine (TAMRA) was purchased from Anaspec. All solvents were of analytical grade and used as received. Dulbecco's modified Eagle's medium (DMEM), fetal bovine serum (FBS), glutaMAX, and antibiotic penicillin-streptomycin (10 000 U  $\text{mL}^{-1}$ ) were obtained from Gibco, and 4',6-diamidino-2-phenylindole dilactate (DAPI) and Prolong Diamond were obtained from Invitrogen. Phalloidin Alexa Fluor 488 was



Susel Del Sol-Fernández

*Congratulations to Nanoscale Horizons on 10 years of inspiring and cutting-edge nanoscience research! It has been a privilege to engage with the Nanoscale Horizons community as a proud member of the Community Board since 2023. We are excited to contribute this article, which uncovers rational design principles for optimizing magnetic hyperthermia agents. It is an exciting time for nanoscale science, and I look forward to seeing how Nanoscale Horizons continues to shape the future of the field in the next decade.*



purchased from ThermoFisher Scientific. Glass 4-well chamber slides were obtained from Nunc™ Lab-Tek.

**2.1.1. Synthesis of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs.** Different ratios of the  $\text{Fe}(\text{acac})_3/\text{Mn}(\text{acac})_2$  precursor (Fe/Mn ratio) were employed to tune the  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  composition from  $x = 0.14$  to  $1.4$  through a one-step thermal decomposition method.<sup>17</sup> The reagent amounts used for all samples are shown in Table S1 in the ESI.† Briefly, 15 mmol of the mixture of metallic precursors at different Fe/Mn ratios was dissolved in 150 mL of benzyl ether (BE) to obtain  $x = 0.14$ ,  $0.20$ , and  $0.37$  MNPs (large-scale synthesis, A Series), while 5 mmol of the metallic precursors, but the same ratios of Fe/Mn were dissolved in 50 mL of BE to obtain the MNPs with  $x = 0.40$ ,  $0.70$  and  $1.4$  (small-scale synthesis, B Series). In the small-scale synthesis, 10 mmol of 1,2-hexadecanediol (HDD) was used, whereas in large scale synthesis, 30 mmol was employed. The oleic acid (OA)/metallic precursor ratio was slightly increased from 2.6 (on large-scale) to 3 (on small scale). The temperature and heating rate at the nucleation and growth steps were maintained invariable in both syntheses. As common steps, the mixture was mechanically stirred (100 rpm) under a smooth  $\text{N}_2$  flow, heated to  $200^\circ\text{C}$  for 2 hours ( $5^\circ\text{C min}^{-1}$ ) and afterwards heated to  $285^\circ\text{C}$  ( $3^\circ\text{C min}^{-1}$ ) for another 2 hours. Finally, the mixture was cooled down to room temperature by removing the heat source. An ethanol excess was added to the mixture, the black material was precipitated and separated with a permanent magnet. The product was then resuspended in hexane, and precipitated with ethanol four times, resulting in a brownish-black hexane dispersion that was stored at  $4^\circ\text{C}$  for future use.

**2.1.2. Water transference.** The transference into water was performed following a previously reported method with slight modifications.<sup>18</sup> In brief, 225 mg of poly(maleic anhydride-*alt*-1-octadecene) (PMAO) was added to a flask containing 195 mL of chloroform and placed in an ultrasonic bath for 30 min at room temperature. Subsequently, 10  $\text{mg}_{\text{Fe}}$  per mL in 5 mL of  $\text{CHCl}_3$  was added dropwise, and the mixture was sonicated for another 15 min. Afterwards, the solvent was slowly removed under vacuum (200 mbar,  $40^\circ\text{C}$ ). The MNPs were then resuspended in 20 mL of NaOH 0.05 M and rota-evaporated (200 mbar,  $70^\circ\text{C}$ ) until complete evaporation of  $\text{CHCl}_3$ . At this point, the solution became clear as MNPs were completely transferred to water. MNPs were then filtered using  $0.22\ \mu\text{m}$  syringe filters. To remove the excess of unbound polymer, the MNP suspension was centrifuged at 24 000 rpm for 2 h four times and finally the MNPs were redispersed in milliQ water for further use.

**2.1.3. Dye functionalization.** To allow *in vitro* tracking, MNPs were labelled with a fluorescent dye (tetramethylrhodamine 5-(and -6)-carboxamide cadaverine (TAMRA)).<sup>19</sup> To do so, 1% of the polymer monomers were modified with TAMRA ( $2\ \text{mg mL}^{-1}$ ) under magnetic stirring overnight in  $\text{CHCl}_3$  before adding the MNPs.

**2.1.4. Functionalization with glucose.** Functionalization with glucose was performed by incubating 1 mg of Fe with 19  $\mu\text{mol}$  of *N*-(3-dimethylaminopropyl)-*N'*-ethylcarbodiimide hydrochloride (EDC) and 30  $\mu\text{mol}$  of 4-aminophenyl  $\beta$ -D-glucopyranoside in

250  $\mu\text{L}$  of SSB buffer pH 9 (50 mM of boric acid and 50 mM of sodium borate). After 3 h of incubation (600 rpm,  $37^\circ\text{C}$ ), the ligand excess was removed by washing the MNPs with phosphate-buffered saline (PBS  $1\times$ ) pH 7.4 in a centrifugal filter with a membrane of the 100 kDa molecular weight limit (Merck Millipore, Darmstadt, Germany) four times. Finally, the MNPs functionalized with glucose were filtered using syringe filters of  $0.22\ \mu\text{m}$  under sterile conditions and stored at  $4^\circ\text{C}$  for further use.

**2.1.5. Structural and colloidal characterization.** The MNPs' size and morphology were evaluated by TEM using a Tecnai T20 (FEI, Netherlands) electron microscope working at an acceleration voltage of 200 kV. TEM samples were prepared by depositing 5  $\mu\text{L}$  of dilute solution on a copper grid (200 mesh) and a posterior drying at ambient temperature prior to analysis. MNP size distributions were obtained by measuring more than 200 MNPs with the Image J software. High resolution transmission electron microscopy (HRTEM), scanning transmission electron microscopy (STEM), and energy-dispersive X-ray (EDX) images were obtained using a Tecnai F30 microscope with an accelerating voltage of 300 kV. Elemental mapping was performed using an Oxford EDS system in the drift corrector acquisition mode.

The crystal structure of the samples was identified by XRD powder patterns recorded using a Bruker D8 ADVANCE diffractometer working with  $\text{CuK}_\alpha$  ( $\lambda = 1.5406\ \text{\AA}$ ) radiation. The patterns were collected between  $10^\circ$  and  $70^\circ$  in the  $2\theta$  range. Crystallite size and lattice strain were determined using the Scherrer formula:

$$d = k\lambda/\beta \cos(\theta) \quad (1)$$

in which the anisotropy constant  $k = 0.94$ ,  $\beta$  is the full width at half maximum (FWHM), and  $\theta$  is the Bragg angle in radians. The Williamson and Hall method was used to obtain size and strain broadening by considering the peak width as a function of  $2\theta$  as

$$\beta \cos \theta = \frac{\kappa \lambda}{D_{\text{W-H}}} + 4\varepsilon \sin \theta \quad (2)$$

where  $\varepsilon$  is the strain component of the crystal lattice, and  $D_{\text{W-H}}$  is the average crystallite size obtained by the W-H analysis. By plotting  $\beta \cos \theta$  on the y axis against  $4 \sin \theta$  on the x axis, and their consequent linearly fitting, we get the strain component from the slope ( $\varepsilon = \text{slope}$ ) and the crystallite size from the intercept ( $i = k\lambda/D_{\text{W-H}}$ ).<sup>20</sup>

The elemental analysis was performed using an inductively coupled plasma optical emission spectrometry (ICP-OES) instrument (PerkinElmer mod. OPTIMA 2100 DV). Typically, 25  $\mu\text{L}$  of the  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs suspension were digested in 1 mL of aqua regia in a volumetric flask at  $60^\circ\text{C}$  overnight. Afterward, the flask was filled up with deionized water.

The surface chemistry was elucidated from FT-IR spectra recorded using a PerkinElmer Spectrum Two spectrometer in the range of  $400\text{--}4000\ \text{cm}^{-1}$ . Samples were lyophilized 24 hours before use.

Thermogravimetric analysis (TGA) of the metal precursors was performed in a PerkinElmer TGAQ5000 instrument from  $40$  to  $500^\circ\text{C}$  at a rate of  $10^\circ\text{C min}^{-1}$  and under a  $\text{N}_2$  flow rate of



25 mL min<sup>-1</sup>. Likewise, the MNP organic contents were determined by TGA using a Universal V4.5A TA instrument; the N<sub>2</sub> flow rate was 50 mL min<sup>-1</sup> and the heating rate was set at 10 °C min<sup>-1</sup> until a final temperature of 800 °C. MNPs in organic solvents were dried in air, while MNPs in water were lyophilized before measured.

The hydrodynamic diameters and zeta potential of the MNPs were measured using dynamic light scattering measurements (Malvern Zetasizer Nano) at room temperature. Samples were prepared at a concentration of 0.05 mg<sub>Fe</sub> per mL in Milli-Q water and sonicated 10 s before measurement.

X-ray photoelectron spectra were recorded with a Kratos AXIS Supra spectrometer equipped with a monochromatic source of Al K $\alpha$  (1486.7 eV) working at 120 W with a base pressure of 10<sup>-9</sup> Torr; the survey spectra were recorded at a pass energy of 160 eV with a step size of 1000 meV, while the high resolution spectra were registered with a step size of 100 meV at pass energies of 20 and 40 eV for metal 2p and 3s regions, respectively. Due to the magnetic nature of the ferrite samples, the magnetic lenses were disabled, and it was operated in the electrostatic-slot mode, setting an analysis area of *ca.* 2 mm  $\times$  1 mm. The powdered samples were measured without any treatment, and the charge neutralizer mode was kept on during the measurements. All spectra were analyzed with the Thermo Avantage software package. The background was described with a Shirley-type equation. Relative atomic contents from the metal 2p region were computed from the Scofield sensitivity factors and the energy compensation factors obtained using the TPP-2M method. The high-resolution spectra in the metal 3s region were fitted with Voigt profiles obtained from a mixture of Gaussian and Lorentzian functions (80/20); details concerning the calculation of the relative atomic concentrations after the fitting procedure are provided in the ESI.<sup>†</sup>

Mössbauer spectra were collected using a constant acceleration spectrometer equipped with a 5 mCi Co57/Rh source. The velocity scale was calibrated with  $\alpha$ -Fe foil and analysed using the MossWinn 4.0 software. Isomer shift values are given with respect to  $\alpha$ -Fe.

## 2.2. Determination of the iron concentration

The determination of the iron concentration was performed following a previously reported protocol,<sup>21</sup> and the iron concentration was adjusted before glucose functionalization. In brief, 5  $\mu$ L of MNPs were diluted in 45  $\mu$ L of solvent (hexane or water) and digested with 100  $\mu$ L of aqua regia solution (3:1 HCl:HNO<sub>3</sub>) at 60 °C for 15 min. Then, the samples were diluted up to 300  $\mu$ L with milliQ water. At this point, 50  $\mu$ L (in triplicate) were used for the iron quantification by mixing the digested samples with 60  $\mu$ L of 0.25 M 1,2-dihydroxybenzene-3,5-disulfonic acid (Tiron). This molecule forms a coloured complex with iron, and it can be investigated by spectrophotometry at  $\lambda$  = 480 nm using a microplate spectrophotometer (BioTek Synergy H1 UV/VIS, Agilent Technologies, Santa Clara, CA, USA) and the results obtained were compared with standard calibration curve results obtained with solutions of known

iron concentrations (0–1000  $\mu$ g Fe per mL). This protocol was performed after each glucose functionalization.

## 2.3. Conventional calorimetry measurement

The determination of magnetic losses from MNP suspensions was performed by non-adiabatic calorimetry measurements using a nanoScale Biomagnetics D5 series device as an AC magnetic field generator. The equipment is composed of a generator with a frequency ranging from 100 to 763 kHz and a magnetic coil (magnetic field range: 0–60 mT). The suspension (1 mL) was placed into a glass vial located at the center of the magnetic induction coil inside an isolating holder. The temperature was measured with an optic fiber sensor Neoptix T1 incorporated into the equipment (measurement range – 40 to 200 °C) for 300 s. Thermal measurements of MNPs in water were performed at 2 mg<sub>Fe+Mn</sub> per mL and 1 mg<sub>Fe+Mn</sub> per mL for low (155 kHz) and high (763 kHz) frequency, respectively. Different magnetic field intensity was used depending on the selected frequency:  $f$  = 763 kHz,  $H$  = 3.8, 8.0, 16.8, 28.8 kA m<sup>-1</sup> and for  $f$  = 155 kHz,  $H$  = 16.8, 28.8 and 44.6 kA m<sup>-1</sup>. The effect of viscosity (1 mL of 0%, 2% and 50% of glycerol in double distilled water) was evaluated for selected samples at  $f$  = 763 kHz. The temperature change was measured as a function of time ( $dT/dt$ ), and the initial linear slope ( $t$  = 30 s) was used to evaluate the heating efficiency in terms of SLP. The SLP values were calculated according to the following expression:

$$SLP = \frac{dT}{dt} \frac{C_d m_d}{m_{Fe+Mn}} \quad (3)$$

where  $C_d$  is the mass specific heat of the dispersion media,  $m_d$  is the mass dispersion,  $m_{Fe+Mn}$  is the iron and manganese masses related to the MNPs diluted in the dispersion and  $dT/dt|_{max}$  is the maximal temperature slope immediately after switching  $H_{AC}$  on. Solvents in our experiment were water ( $C_{d,water} = 4.18$  J g<sup>-1</sup> °C<sup>-1</sup>) or water with different glycerol fractions from 0 to 50%, considering  $C_{d,glycerol} = 2.43$  J g<sup>-1</sup> °C<sup>-1</sup> and for mixed water-glycerol  $C_{d,mix} = 3.30$  J g<sup>-1</sup> °C<sup>-1</sup>. The sample volume employed for the experiment was 1 mL.

## 2.4. Magnetic measurements

Static conditions: magnetic characterization of MNPs under static conditions was carried out using a superconducting quantum interference device (SQUID, Quantum Design) magnetometer at distinct temperatures from 5 K up to 300 K fields up to 4000 kA m<sup>-1</sup>. The studied magnetic suspensions were lyophilized to get a powder, which was put into a gelatin capsule ( $\sim$ 5 mg per sample), and immobilized with cotton wool. Magnetization units were normalized to the organic content measured by TGA. Saturation magnetization ( $M_s$ ) values were calculated by extrapolating to infinite field the experimental results obtained in the high field range where the magnetization linearly increases with 1/H.

Dynamical conditions: AC magnetometry measurements of the studied magnetic suspensions ( $m_{Fe+Mn} = 5$  mg) were carried out using commercial inductive magnetometers (Advance AC Hyster Series; Nanotech Solutions, Spain) at 150 kHz and



300 kHz and field intensities up to  $24 \text{ kA m}^{-1}$ . Each magnetization cycle is obtained out of three repetitions, resulting in the averaged magnetization cycle, related magnetic parameters ( $H_C$ ,  $M_R$ , Area) and magnetic losses. SAR values were determined using the expression.<sup>22</sup>

$$\text{SAR} = Af \quad (4)$$

where  $A$  is the AC magnetic area and  $f$  is the AC magnetic field frequency. Magnetization units were normalised by the magnetic mass (*i.e.* iron plus manganese masses).

## 2.5. Biological assays

**2.5.1. Cell culture.** MIA PaCa-2 human and male pancreatic adenocarcinoma cells (ATCC<sup>®</sup> number CRL-1420) were cultured in Dulbecco's modified Eagle's medium (DMEM) supplemented with 10% fetal bovine serum, 5% L-glutamine, and 5% penicillin/streptomycin antibiotics and maintained in a humidifier incubator at  $37^\circ\text{C}$  in a 5%  $\text{CO}_2$  atmosphere.

**2.5.2. In vitro cytotoxicity assay.** MTT assay was performed to evaluate cell viability of MNP-treated cells. MIA PaCa-2 cells were seeded in 96-well plates and cultured for 24 h ( $5 \times 10^3$  cells per well). MNPs functionalized with glucose were added in DMEM at various concentrations (25, 50, 100, and  $150 \mu\text{g Fe per mL}$ ) and incubated for 24 h at  $37^\circ\text{C}$ . After treatment, cells were thoroughly washed with PBS, and  $10 \mu\text{L}$  of MTT solution ( $5 \text{ mg mL}^{-1}$  in PBS) in a final volume of  $100 \mu\text{L}$  (DMEM w/o phenol red) was added to each well. Following 30 min of incubation at  $37^\circ\text{C}$ , the plates were centrifuged at 1250 rpm for 30 min and formazan salts were dissolved with  $100 \mu\text{L}$  of DMSO in agitation for 15 min at  $37^\circ\text{C}$ ; the resulting absorbance was determined at  $\lambda = 540 \text{ nm}$  on a microplate reader (BioTek Synergy H1 Multimode Microplate Reader). Control cells without MNPs (negative control) were also analysed. Data are expressed as the percentage of cell viability normalized for the control condition and are the results of three independent biological replicates.

**2.5.3. Internalization by fluorescence microscopy.** MNP internalization was studied by fluorescence microscopy (using MNPs modified with TAMRA fluorophore) and ICP-OES. Fluorescence microscopy: to perform fluorescence microscopy analysis,  $5 \times 10^4$  cells were seeded on a glass 4-well chamber slide. After 24 h of culturing, cells were treated with  $100 \mu\text{g Fe per mL}$  of MNPs functionalized with glucose and incubated at  $37^\circ\text{C}$  (5%  $\text{CO}_2$ ) for 24 h. Noninternalized MNPs were removed by washing with PBS thrice. Cells were fixed with 4% of paraformaldehyde for 15 min at room temperature and washed twice with cold PBS. After that, F-actin staining was performed using phalloidin AlexaFluor 488 following manufacturer's instructions. For nuclei labelling, cells were incubated 10 min at room temperature with  $0.6 \mu\text{M}$  of DAPI. Finally, the slide was mounted using ProLong mountant medium. Fluorescence microscopy images were obtained using an inverted microscope (Nikon Eclipse Ti-E, Amsterdam, The Netherlands).

## 2.6. Statistical analysis

All data are presented as mean  $\pm$  standard deviation (SD). One-way analysis of variance (ANOVA) and the Tukey post-hoc test were applied to calculate the differences between the values. Values of  $p < 0.05$  were considered statistically significant.

# 3. Results and discussion

## 3.1. Design of a library of $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$ MNPs. Structural changes as a result of manganese substitution

Several  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with different  $\text{Mn}^{2+}$  content but similar sizes and shapes were synthesized by a one-step thermal decomposition method, modifying different parameters such as the metallic precursors ratio ( $\text{Fe}(\text{acac})_3/\text{Mn}(\text{acac})_2$ ), the surfactant/precursors ratio (OA/metallic precursors) and/or the final solvent volume (see Table S1 in the ESI<sup>†</sup>). In all cases, the remaining synthetic parameters, that is, the heating rate, the reaction time, and the temperatures during the nucleation and growth steps, were maintained constant. Benzyl ether (BzE) was selected as a passive solvent due to its lack of hydroxyl groups capable of iron chelation, thereby minimizing a direct influence on the MNPs' size and shape.<sup>23</sup>

To elucidate the influence of the surfactant concentration on the overall composition, two  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs were synthesized using the same  $\text{Fe}(\text{acac})_3/\text{Mn}(\text{acac})_2$  ratio (6.5) and a final solvent volume ( $50 \text{ mL}$ ), while slightly varying the OA/metallic precursor ratio from 2.6 to 3 (see Table S2 in the ESI<sup>†</sup>). The empirical  $x$  value, determined by ICP-OES, remained unchanged for both samples ( $x_{\text{Empiric}} = 0.18$ ), indicating that under these synthetic conditions  $\text{Mn}^{2+}$  incorporation was insensitive to slight variations in the amount of surfactant. However, the sample synthesized using lower OA/metallic precursor ratios exhibited more irregular shapes (Fig. S1 in the ESI<sup>†</sup>). A plausible explanation is that limited OA availability leads to a preferential growth of the initial seeds along certain crystal directions (particularly those normal to the facets  $\{111\}$  and  $\{110\}$ , which are poorly stabilized by the OA, resulting in more irregular shapes. In contrast, sufficient OA during the nanocrystal growth ensures well-capped and stabilized crystal facets, leading to MNPs with controlled faceted shapes.<sup>24,25</sup>

The overall composition of the MNPs was then varied by changing the metallic precursor ratio and final solvent volume. Two series of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs were synthesized: A Series (large-scale synthesis), where the MNPs were prepared in  $150 \text{ mL}$  of BzE, and B Series (small-scale synthesis) obtained using  $50 \text{ mL}$  of BzE. The  $\text{Mn}^{2+}$  content in both series was adjusted by changing the initial  $\text{Fe}(\text{acac})_3/\text{Mn}(\text{acac})_2$  ratios, corresponding to theoretical  $x$  values of 0.40, 0.75, and 1.0 (Table S1 in the ESI<sup>†</sup>). In all cases,  $\text{Mn}^{2+}$  incorporated into the final MNPs was much lower than the theoretical values, based on the amount of  $\text{Mn}^{2+}$  added as initial precursor. This effect has already been described and is likely due to various factors, such as differences in the decomposition temperatures of the two precursors (most of the  $\text{Mn}(\text{acac})_2$  decomposes at temperature of approximately  $60^\circ\text{C}$  higher than that of  $\text{Fe}(\text{acac})_3$ ,



**Table 1** Summary of Fe(acac)<sub>3</sub>/Mn(acac)<sub>2</sub> molar ratios employed in the synthesis and theoretical ( $x_{\text{Theo}}$ ) and empirical ( $x_{\text{Empiric}}$ ) stoichiometries of the Mn<sub>x</sub>Fe<sub>3-x</sub>O<sub>4</sub> ferrites. The average sizes were determined by TEM ( $D_{\text{TEM}}$ ). Peak position at 311 reflection and crystallite sizes determined by XRD using the Sherrer equation ( $D_{\text{XRD}}$ ) or Williamson–Hall method ( $D_{\text{W-H}}$ )

| Samples           | Fe/Mn precursors' molar ratio in synthesis | $x_{\text{Theo}}$ value | $x_{\text{Empiric}}$ value | Measured formula                                     | $D_{\text{TEM}}$ (nm) ± SD | (311) peak pos. ( $2\theta^\circ$ ) | $D_{\text{XRD}}^a$ (nm) ± SD | $D_{\text{W-H}}^b$ (nm) ± SD |
|-------------------|--------------------------------------------|-------------------------|----------------------------|------------------------------------------------------|----------------------------|-------------------------------------|------------------------------|------------------------------|
| A Series (150 mL) | 6.5                                        | 0.40                    | 0.14                       | Mn <sub>0.14</sub> Fe <sub>2.86</sub> O <sub>4</sub> | 14 ± 3                     | 35.43                               | 12 ± 1                       | 12 ± 1                       |
|                   | 3                                          | 0.75                    | 0.23                       | Mn <sub>0.23</sub> Fe <sub>2.77</sub> O <sub>4</sub> | 13 ± 3                     | 35.40                               | 13 ± 1                       | 18 ± 2                       |
|                   | 2                                          | 1.0                     | 0.37                       | Mn <sub>0.37</sub> Fe <sub>2.63</sub> O <sub>4</sub> | 15 ± 2                     | 35.39                               | 14 ± 2                       | 15 ± 1                       |
| B Series (50 mL)  | 6.5                                        | 0.40                    | 0.18                       | Mn <sub>0.18</sub> Fe <sub>2.82</sub> O <sub>4</sub> | 13 ± 2                     | 35.42                               | 14 ± 1                       | 15 ± 1                       |
|                   | 3                                          | 0.75                    | 0.47                       | Mn <sub>0.47</sub> Fe <sub>2.53</sub> O <sub>4</sub> | 15 ± 1                     | 35.39                               | 13 ± 1                       | 16 ± 2                       |
|                   | 2                                          | 1.0                     | 0.70                       | Mn <sub>0.70</sub> Fe <sub>2.30</sub> O <sub>4</sub> | 14 ± 2                     | 35.35                               | 13 ± 1                       | 16 ± 1                       |
|                   | 1                                          | 1.5                     | 1.40                       | Mn <sub>1.40</sub> Fe <sub>1.60</sub> O <sub>4</sub> | 14 ± 1                     | 35.26                               | 13 ± 1                       | 15 ± 2                       |

<sup>a</sup> Calculated using the Scherrer method. <sup>b</sup> Calculated using the Williamson–Hall method.

see Fig. S6 left panel in the ESI†) and/or the ionic radii differences between Mn<sup>2+</sup> and Fe<sup>2+</sup>.<sup>16,26</sup> However, this effect was not observed in other studies when using the same metallic precursors<sup>3,13</sup> or oleates.<sup>2</sup> Nevertheless, in the latter, octadecene was used as the synthetic solvent instead of BzE, making a direct comparison difficult. Moreover, it should be noted that in both series of MNP samples (A and B), the higher the molar concentration of the Mn<sup>2+</sup> precursor used in the synthesis, the higher the Mn content in the final ferrite stoichiometry (Table 1). This tendency, determined by ICP-OES, was further confirmed by EDX for samples belonging to A Series (Fig. S2 in the ESI†).

Additionally, the solvent volume influenced the incorporation of Mn<sup>2+</sup> into the spinel structure (Fig. S3 in the ESI†). When the same Fe(acac)<sub>3</sub>/Mn(acac)<sub>2</sub> ratio was used, the amount of Mn<sup>2+</sup> incorporated into the spinel structure was consistently higher in the B Series (smaller volume of solvent) than in A Series (larger solvent volume) (Table 1). One hypothesis is that the use of a smaller solvent volume facilitates higher and more uniform temperatures throughout the mixture, improving the decomposition of the Mn(acac)<sub>2</sub> precursor and thereby reducing the critical gap between the decomposition of metallic precursors and the saturation limit for particle nucleation.<sup>27</sup> To further increase the Mn<sup>2+</sup> content in the final MNPs, an additional synthesis was performed only for Serie B, as was the one incorporating more Mn<sup>2+</sup> in the final structure ( $x_{\text{Theo}} = 1.5$ , Mn<sub>1.50</sub>Fe<sub>1.50</sub>O<sub>4</sub>). The empirical  $x$  value was similar to the theoretical one ( $x_{\text{Empiric}} = 1.40$ , Mn<sub>1.40</sub>Fe<sub>1.60</sub>O<sub>4</sub>).


As shown in Fig. 1A and Table 1, all the synthesis yielded MNPs with similar polyhedral morphologies and sizes ranging from 13 to 15 nm, regardless of the metallic precursor's ratio or the solvent volume used. These results are in good agreement with previous works using the same precursors but different synthetic methods.<sup>13,16,28</sup> Controlling the particle size and shape is crucial to isolate and accurately assess the influence of composition on the anisotropy and magnetic heating, while minimizing the influence of these parameters.

To investigate whether the tuned compositions could result in a single or core/shell MNP structure as previously reported,<sup>29,30</sup> we carried out STEM-energy-dispersive X-ray spectroscopy analysis of selected Mn<sub>x</sub>Fe<sub>3-x</sub>O<sub>4</sub> MNPs with the lowest, medium, and

highest Mn<sup>2+</sup> content ( $x_{\text{Empiric}} = 0.14$ , 0.70 and 1.40 respectively) (Fig. 1B). The chemical maps showed the presence of Mn and Fe signals along the magnetic cores and the absence of a marked core-shell structure, thus, confirming the successful synthesis of a unique Mn<sub>x</sub>Fe<sub>3-x</sub>O<sub>4</sub> core in agreement with several reports.<sup>2,3,16</sup>

For further analysis, we selected samples with increasing Mn<sup>2+</sup> content, that is,  $x_{\text{Empiric}} = 0.14$ , 0.23, 0.37, 0.47, 0.70, and 1.40. Fig. 2A shows the evolution of the XRD patterns of these MNPs together with the positions of the peaks corresponding to the MnFe<sub>2</sub>O<sub>4</sub> spinel-type phase (PDF file 96-230-0619 in the ICDD powder diffraction file database). Interestingly, the presence of additional reflections (denoted with an asterisk) corresponding to the Fe<sub>1-x</sub>O phase (PDF file 96-101-1199) appeared for the samples with Mn<sup>2+</sup> content  $x \geq 0.70$ . The coexistence of both magnetic phases can have a high impact on the structural, magnetic, and heating properties of ferrite MNPs, as previously reported.<sup>3,31,32</sup> As expected, we found a gradual shift toward lower angles while increasing the Mn<sup>2+</sup> content from 35.43 ( $x_{\text{Empiric}} = 0.14$ ) to 35.26 ( $x_{\text{Empiric}} = 1.40$ ), taking as reference the reflection (311). This corresponds to an increase in the cubic unit cell parameter due to the substitution of smaller host ions (0.65 Å for Fe<sup>3+</sup> and 0.78 Å for Fe<sup>2+</sup>) by a larger Mn<sup>2+</sup> (0.83 Å),<sup>33</sup> and to the appearance of strains inside the spinel structure.<sup>2,20</sup> To further confirm this hypothesis, we calculated the strain ( $\epsilon$ ) component inside the spinel structure following the Williamson–Hall (W–H) method<sup>33</sup> using XRD patterns and measuring the lattice distance for selected samples by HRTEM.<sup>33</sup> As shown in the HRTEM images (Fig. 2B), the inverse FFT of the (220) plane distance increased from 0.286 nm ( $x_{\text{Empiric}} = 0.23$ ) to 0.290 nm ( $x_{\text{Empiric}} = 0.37$ ), in agreement with the XRD patterns. On the other hand, from the fitting of the W–H plot, we found that when the Mn<sup>2+</sup> content increased from  $x_{\text{Empiric}} = 0.14$  up to 1.40, the lattice strain increased from  $0.20 \times 10^{-3}$  to  $2.12 \times 10^{-3}$  (Table S3 in the ESI†), indicating a larger lattice spacing due to the introduction of Mn<sup>2+</sup>. This ultimately leads to the appearance of uniform tensile strain,<sup>20</sup> which corresponds to the left shift shown in the XRD patterns (Fig. 2A). Although the lattice defects varied among the samples, the effect was more prominent for the sample with the highest content of Mn<sup>2+</sup> (Mn<sub>1.40</sub>Fe<sub>1.60</sub>O<sub>4</sub>).



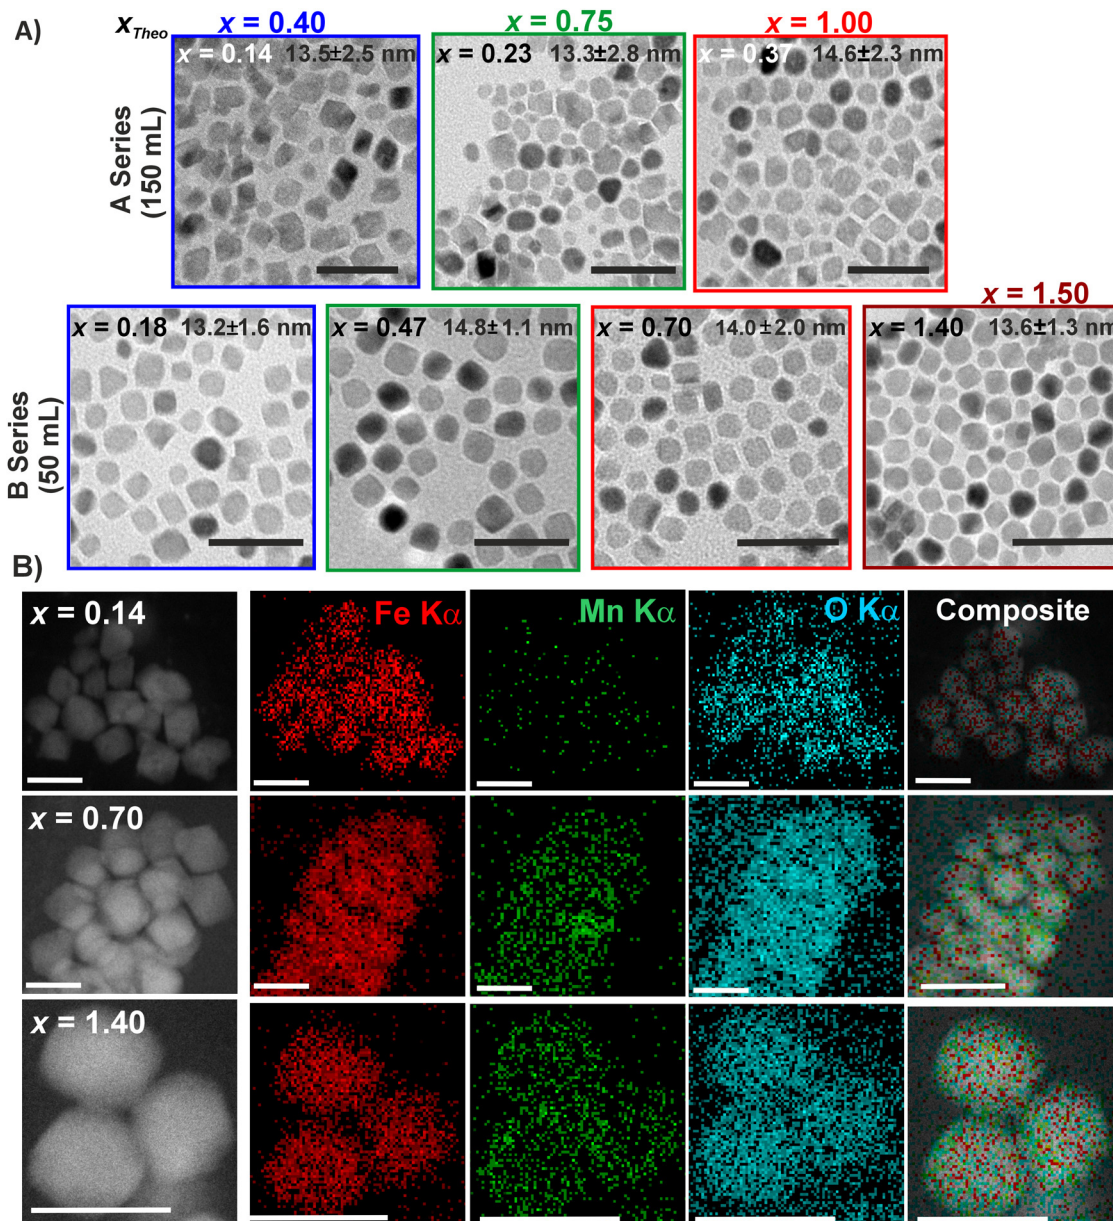

**Fig. 1** (A) TEM images of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with varying  $\text{Mn}^{2+}$  content ( $x_{\text{Empirical}} = 0.14$  to  $1.40$ ). The samples with the initial Fe/Mn precursor amount of  $x_{\text{Theo}} = 0.40, 0.75, 1.0$ , and  $1.50$  are highlighted with blue, green, red, and brown boxes, respectively. Inset: Empirical  $x$  value for each sample determined by ICP-OES along with their respective size diameters. Scale bar: 50 nm. (B) STEM-EDX mapping images of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with the lowest, medium, and highest content of  $\text{Mn}^{2+}$  ( $x_{\text{Empirical}} = 0.14, 0.70, 1.40$ ). Scale bar: 50 nm ( $x_{\text{Empirical}} = 0.14$  and  $0.70$ ), 20 nm ( $x_{\text{Empirical}} = 1.40$ ).

The average crystallite sizes calculated using Scherrer's formula ( $D_{\text{XRD}}$ ) and the W-H method ( $D_{\text{W-H}}$ ) ranged from 12 nm to 14 nm and from 12 nm to 18 nm, respectively (Table 1). In all cases, the mean MNP diameters obtained from TEM ( $D_{\text{TEM}}$ ) matched relatively well with the crystal sizes determined by XRD using both methods, indicating a single-crystal structure. No clear correlation between the  $\text{Mn}^{2+}$  content and the crystallite size was observed. Similar findings have been reported for  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  nanoparticles with homogeneous characteristics ( $\sim 6$  nm in size, uniform shape, and oleic acid coating) in the range of  $x = 0.11$  to  $0.49$ .<sup>12</sup> In contrast, other works have reported an increase of the crystallite size

for  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs obtained by a similar synthetic procedure but using 1-octadecene as a solvent, or by co-precipitation in water using metallic chloride precursors.<sup>4,13</sup> In contrast, a decrease in the crystallite size from 16.7 nm ( $x = 0$ ) to 10.2 nm ( $x = 1$ ) has been observed for Mn-doped  $\text{CoFe}_2\text{O}_4$  ferrites.<sup>34</sup> These discrepancies may be attributed to structural defects frequently associated with the increase of  $\text{Mn}^{2+}$  in the spinel structure, which could cause contraction of the crystal structure. In our case, the use of BzE as the solvent, rather than more reducing solvents like 1-octadecene, likely helped minimize the formation of such defects.<sup>3</sup> Therefore, even when an increase in the  $\text{Mn}^{2+}$  content may have introduced some

strain defects, these were insufficient to impact the final crystallite size of our MNPs.

### 3.2. Manganese substitution induces changes in the oxidation state, relocation of cations, and sample heterogeneity

To shed light on the oxidation state of the cations in the samples under study, we analyzed the photoelectron spectral region corresponding to the Mn 3s and Fe 3s region using X-ray photoelectron spectroscopy (XPS). The fitting results for the  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with  $x_{\text{Empiric}} = 0.23, 0.37, 0.47, 0.70$ , and 1.40 are shown in Fig. S5 and summarized in Table S4 of the ESI;† also, a detailed explanation of the spectral features found in this region is provided in Section S1 of the ESI.†

All spectra were successfully fitted with two sets of doublets and a minor contribution at higher binding energy (BE). The doublet with the lower BEs (80–90 eV) corresponds to Mn cations, and the one with higher BEs (90–100 eV) is attributed to Fe cations. The occurrence of these doublets is primarily due to the multiplet splitting of the ionic final-state configuration  $3s^13d^n$ , arising from the exchange interactions between the remaining 3s core-electron and the unpaired electrons in the valence 3d shell of the transition metals.<sup>35–37</sup> This interaction gives rise to high spin (lower BE) and low spin (higher BE) final-state configurations, where the electron spins in the 3s and 3d shells are coupled either parallel or anti-parallel, respectively. Since the magnitude of the resulting energy splitting ( $\Delta\text{BE}$ ) is proportional to the total spin density of the 3d shell, this value has been used to identify the oxidation state of the ion,<sup>38,39</sup> especially for compounds with high degree of ionicity. In addition, as the  $\Delta\text{BE}$  is also proportional to the exchange integral between the 3s and 3d shells, it could be sensitive to covalent and ligand field effects.<sup>40,41</sup>

Fig. 2C shows the behavior of the computed  $\Delta\text{BE}$  values after spectral fitting. Remarkably, a close correlation between the energy splittings of both Mn 3s and Fe 3s doublets is apparent. For the samples with  $x_{\text{Empiric}} \leq 0.37$ , the splitting of the Mn 3s doublet is higher than 6.2 eV, which strongly suggests that the manganese ions are preferentially in the divalent state, with no evidence of oxidized species.<sup>39,42</sup> These values are consistent with the results reported elsewhere for several manganese ferrites.<sup>43,44</sup> At these low  $\text{Mn}^{2+}$  levels ( $x_{\text{Empiric}} \leq 0.37$ ), the recorded values of  $\Delta\text{BE}$  for the Fe 3s doublet around 6.2–6.3 eV suggest the coexistence of  $\text{Fe}^{2+}$  and  $\text{Fe}^{3+}$  cations due to the partial substitution of  $\text{Mn}^{2+}$  in the ferrite structure.<sup>36,37,40,41</sup> It is worth noting that, as the  $\text{Mn}^{2+}$  content in the ferrites increases (e.g., in samples with  $x_{\text{Empiric}} = 0.47$  and 0.70), a gradual decrease in  $\Delta\text{BE}$  of the Mn 3s doublet is observed. Such behavior could be related to either the appearance of a small fraction of Mn in a higher oxidation state ( $x_{\text{Empiric}} \geq 0.70$ ) or a less ionic environment of the  $\text{Mn}^{2+}$  ions in the spinel structure,<sup>45,46</sup> which could suggest: (i) a gradual occupancy of tetrahedral sites by  $\text{Mn}^{2+}$  or (ii) a higher probability of  $-\text{Mn}^{2+}-\text{O}-\text{Mn}^{2+}-$  sequences at the expense of  $-\text{Mn}^{2+}-\text{O}-\text{Fe}^{3+}-$  sequences. At the same time, the splitting of the Fe 3s doublet increases, which is consistent with the progressive substitution of  $\text{Fe}^{2+}$  cations by  $\text{Mn}^{2+}$  in the spinel structure. In the case of the

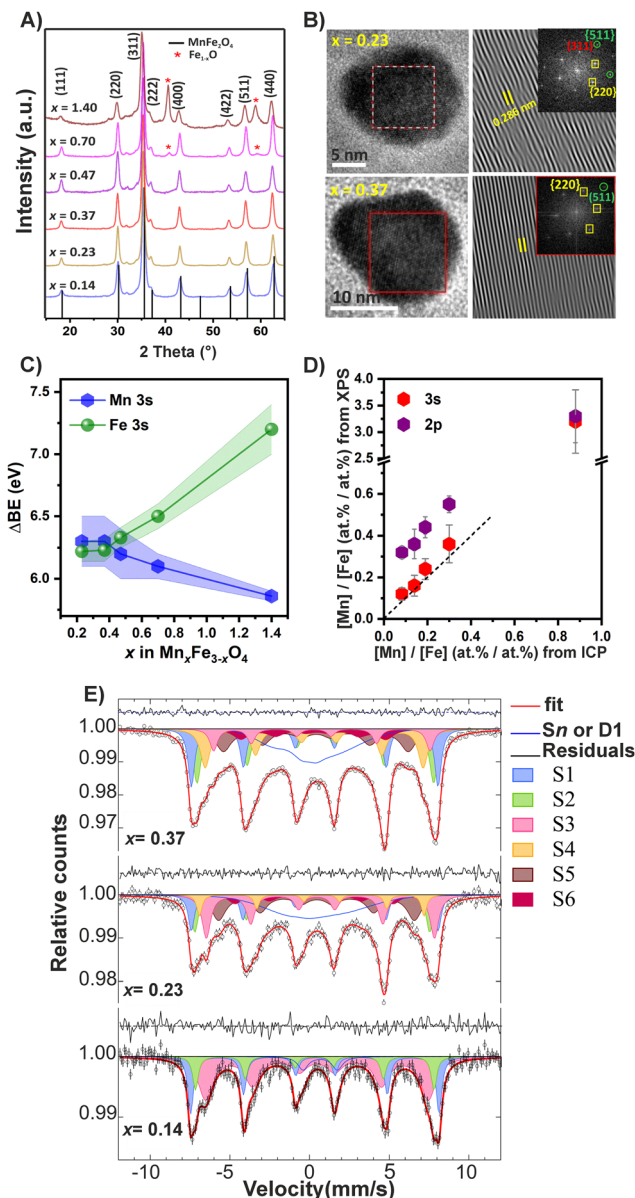


Fig. 2 (A) Evolution of the XRD pattern of the full set of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with  $x = 0.14$  up to 1.40 with the corresponding Bragg positions of  $\text{MnFe}_2\text{O}_4$  reference (black lines) and  $\text{Fe}_3\text{O}_4$  (red asterisk). (B) HRTEM images of samples with  $x_{\text{Empiric}} = 0.23$  and 0.37 and their FFT and inverse FFT of the plane (220). (C) Energy splitting of the Mn 3s and Fe 3s doublets as a function of the ferrite stoichiometry computed from XPS. (D) Mn/Fe atomic ratios computed from the 2p and 3s XPS signals vs. the compositional data obtained from ICP, for the samples with ferrite stoichiometries of  $x_{\text{Empiric}} = 0.23, 0.37, 0.47$  and 1.40. (E) Mössbauer spectra of  $x_{\text{Empiric}} = 0.14, 0.23$  and 0.37 MNPs.

sample with the highest  $\text{Mn}^{2+}$  content ( $x_{\text{Empiric}} = 1.40$ ), the further reduction of the Mn 3s  $\Delta\text{BE}$  to 5.9 eV may indicate the coexistence of a  $\text{Mn}^{3+}$  fraction forming oxidized species. Meanwhile, the high value for the Fe 3s  $\Delta\text{BE}$  (7.2 eV) indicates the predominant presence of  $\text{Fe}^{3+}$  cations inside the oxygen lattice consistent with a highly ionic environment.<sup>36,40,41,47</sup> This observation suggests a preferential occupancy of the octahedral sites (B) by  $\text{Fe}^{3+}$ .<sup>45,46</sup> Additionally, the likely absence of  $\text{Fe}^{2+}$  ions

is consistent with a massive substitution of Mn in the ferrite structure.

The recorded XPS spectra also provided a conclusive clue on the heterogeneity of the samples by analyzing the 2p and 3s signals of the cations. We have computed the Mn/Fe atomic ratios from the spectral fittings of the 3s region (Section S1 in the ESI†) and the direct integration of the corresponding 2p high-resolution spectra (see Fig. S4 in the ESI†). Using the TPP-2 formula previously reported,<sup>48</sup> it is possible to estimate the inelastic mean free path (IMFP) of the photoelectrons coming from both spectral regions, which is a function of the photoelectron kinetic energy. For the Mn and Fe 3s photoelectrons with kinetic energy around 1400 eV, the IMFP is roughly 2.1 nm; in the case of the Mn and Fe 2p photoelectrons with kinetic energy about 800 eV, the IMFP is roughly 1.4 nm. Therefore, the information depth (3 times the IMFP) derived from the 2p and 3s signals covers the outermost 4 nm (2p) and the topmost 6 nm (3s) of the ferrite MNPs, respectively. The comparison between the computed Mn/Fe atomic ratios is displayed graphically in Fig. 2D, where both data sets derived from XPS are plotted against the Mn/Fe ratios obtained by ICP quantification. The dashed line with a unitary slope represents the ideal case where the surface composition computed by XPS agrees with the overall composition of the MNPs (ICP). From the graph, it is apparent that for the samples with  $x_{\text{Empiric}} \leq 1.40$ , the estimated cation composition along the outermost 6 nm of the MNP (3s) is similar to the composition from the ICP data, which is consistent with the estimated average MNP diameters of 13–15 nm from TEM and DRX measurements. The fact that the 3s data are slightly biased toward higher Mn content in all samples could suggest that the Mn ions entering the ferrite structure do not reach the very core of the MNPs. On the other hand, by comparing the data sets from the 2p and 3s signals, it is noticeable that for  $x_{\text{Empiric}} \leq 1.40$  the Mn/Fe atomic ratio is systematically higher in the first 4 nm than if it is computed extending the probed depth for other 2 nm inside the MNP core. In other words, the nanoparticle's surface is enriched in the Mn<sup>2+</sup> content with respect to the deeper zones near the core. This fact could indicate that the incorporation of Mn into the ferrite structure starts in the most superficial layers and then extends toward the interior of the MNPs.

Previous works<sup>50–52</sup> on doped ferrites have also reported this surface enrichment of the doping element, which seems to be related to differing onsets of the nucleation process: when the nucleation step of the doping-containing monomers occurs late compared to the nucleation of the matrix-containing monomers, the doping element is initially out of the core of the resulting particle, and can develop a gradient concentration as a function of its diffusivity across the particle. This phenomenon is triggered by the aforementioned 60 °C difference in the decomposition temperature between Mn<sup>2+</sup> and Fe<sup>3+</sup> acetylacetonates, which produces monomers at different stages of the reactions that nucleate inhomogeneously. A thorough understanding of the magnitude of Mn gradient along the nanoparticle structure as a function of ferrite stoichiometry requires more in-depth studies using STEM-EELS and XPS combined with Ar ion cluster sputtering, which will be the subject of future work.

### 3.3. Mn substitution and heterogeneity in the Mn content along the MNPs dictate the predominant magnetic relaxation regime

To elucidate the impact of compositional heterogeneity and Mn substitution on the magnetic behaviour, we recorded Mössbauer spectra at room temperature. Fig. 2E shows the corresponding spectra for samples with  $x_{\text{Empiric}} = 0.14, 0.23$  and  $0.37$ . The general aspect of the spectra is different from that of bulk  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$ <sup>49</sup> and similar to that of nanostructured ferrite MNPs.<sup>50</sup> At first sight, it is apparent that the samples display magnetic order, owing to the hyperfine peaks that dominate the profiles; in addition, the occurrence of a broad central background, especially for the samples with higher Mn<sup>2+</sup> content, could indicate the presence of partially superparamagnetic (SPM) components.<sup>50</sup> The simultaneous presence of both features shows that the MNPs cannot be simply described as homogeneous with a constant Mn<sup>2+</sup> concentration, and thus the same magnetic behaviour throughout the particle or in all the particles. Therefore, we tried an analysis intending to separate the ferrimagnetic (FiM) behaviour from the SPM-like one by considering: (1) sextets with hyperfine fields (HF) above a threshold value of 40 T (FiM portion contribution),<sup>50–52</sup> and (2) sextets with lower HF values and poorly structured central contributions (fraction with SPM-like behaviour). These last features could include either a broad singlet, or a quadrupolar doublet, or a Voigt-based Gaussian distribution of HFs and isomer shifts (IS);<sup>53</sup> this type of distribution can provide flexibility to the fits to simulate more complex structures at the centre of the spectrum.

The results of the fits are shown in Fig. 2E and summarized in Table S10 of the ESI.† For the sample with  $x_{\text{Empiric}} = 0.14$ , the spectrum was successfully fitted with three hyperfine sextets and a small quadrupolar doublet. The two sextets with higher HFs and IS values around  $0.3 \text{ mm s}^{-1}$  are attributed to Fe<sup>3+</sup> ions; the one displaying the largest HF (S1) corresponds to the cations that occupy A sites, while the other sextet (S2) is assigned to the cations occupying the B sites. The third sextet (S3) with a lower HF (*ca.* 43 T) and an IS near  $0.5 \text{ mm s}^{-1}$  can be attributed to the fictitious intermediate state Fe<sup>2.5+</sup> due to the fast electron hopping between adjacent Fe<sup>2+</sup> and Fe<sup>3+</sup> cations along the B sites of the cubic spinel, above the Verwey temperature. As can be seen, the emergence of S2 is due to the imbalance between Fe<sup>2+</sup> and Fe<sup>3+</sup> cations due to the partial substitution of Fe<sup>2+</sup> by Mn<sup>2+</sup> in the ferrite structure. For the other two measured samples ( $x_{\text{Empiric}} = 0.23$  and  $0.37$ ), additional sextets (S4–S6) were required. S4 is attributed to Fe<sup>2.5+</sup> states where the Fe<sup>2+</sup> and Fe<sup>3+</sup> cations have different local environments with respect to those in S3 due to the emergence of inequivalent sites for Fe cations, *i.e.*, the gradual incorporation of Mn<sup>2+</sup> ions modifies the nearest-neighbor surroundings of Fe cations along the ferrite lattice. In contrast, S5 and S6 have large peak widths and HFs below the threshold value (40 T) for FiM behavior, indicating that these contributions encompass a fraction of Fe<sup>3+</sup> and Fe<sup>2.5+</sup> sites where the effective magnetic moment is no longer in a blocked FiM state, but it begins to fluctuate at a frequency that is on the order of the inverse of the Mössbauer characteristic time.



The rest of the spectral area contains only a broad quadrupolar doublet D1 (for the sample with  $x_{\text{Empiric}} = 0.14$ ), or a distribution of HF values  $S_n$  (for the samples with  $x_{\text{Empiric}} = 0.23$  and  $0.37$ ); such distribution is similar in both samples, with IS values centered at  $0.3 \text{ mm s}^{-1}$ , pointing to a dominant contribution from  $\text{Fe}^{3+}$  cations and consistent with high  $\text{Mn}^{2+}$  substitution. The relative area of D1 is small in the  $x_{\text{Empiric}} = 0.14$  sample (below 6%), while for the samples with higher  $\text{Mn}^{2+}$  concentration the overall contribution from  $S_n$  plus  $S_5$  and  $S_6$  sextets drastically increases above 40%. As was mentioned before, these spectral features indicate the occurrence of SPM relaxation, which can be the result of either small MNPs or MNPs with low magnetic anisotropy. Since the three samples exhibit similar size distributions, it is likely that the differences between them mostly arise from anisotropy effects across the particles. Indeed, the fact that the SPM contribution is more important for the samples with higher  $\text{Mn}^{2+}$  content strongly suggests that substitution of  $\text{Fe}^{2+}$  by  $\text{Mn}^{2+}$  in the ferrite lattice induces a decrease of the superexchange interactions,<sup>51</sup> that is reflected in lower values of the magnetic anisotropy<sup>54,55</sup> (see the next section). Moreover, since the XPS results point to a gradient of concentration with a large  $[\text{Mn}]/[\text{Fe}]$  molar fraction on the outermost part of the MNPs, it is likely that such SPM relaxation occurs preferentially on the surface of the MNPs. Hence, it can be inferred that sextets  $S_1$ – $S_4$  are associated with the inner part of the MNPs, *i.e.* the MNP cores exhibit FiM behavior at room temperature. Such a finding is further confirmed by estimating the ferrite stoichiometry from the relative area of these four contributions: the  $[\text{Mn}]/[\text{Fe}]$  molar ratio is 0.08, 0.13 and 0.20 for  $x_{\text{Empiric}} = 0.14$ , 0.23 and 0.37, respectively; these values are very close to those obtained from the 3s XPS data (*cf.* Fig. 2D), which provide information on the inner part of the MNPs, as has been pointed out.

### 3.4. Manganese substitution controls anisotropy and soft ferrite transition

The influence of  $\text{Mn}^{2+}$  substitution on the static magnetic properties was analyzed by recording the hysteresis curves at

300 K using a superconducting quantum interference device (SQUID), as described in the Experimental section. Magnetization values were normalized to the organic content measured by TGA (Fig. S6 right panel in the ESI†) and all the magnetic parameters are presented in Table S5 of the ESI.† Overall, the MNPs showed a SPM behavior at room temperature with negligible remanence or coercivity (Fig. 3). The transition from the FiM to SPM regime stated by Mössbauer spectroscopy is not evidenced here due to the differences in the time windows for both measurements ( $\sim 10^{-8}$  vs.  $10^2$  s). The magnetization values were nearly constant when the  $\text{Mn}^{2+}$  content varied between  $x_{\text{Empiric}} = 0.14$ – $0.70$  ( $80$ – $82 \text{ A m}^2 \text{ kg}_{\text{ferrite}}^{-1}$ ) while decreased for  $x_{\text{Empiric}} = 1.40$  ( $61 \text{ A m}^2 \text{ kg}_{\text{ferrite}}^{-1}$ ) (Fig. 3A). Our results are in agreement with the work reported by Li *et al.*, where a series of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with  $x = 0.11$  up to  $0.49$ , and similar particle and crystal sizes ( $\sim 8.0 \text{ nm}$ ) showed very similar  $M_s$  values and blocking temperatures despite the differences in composition.<sup>12</sup> It is worth noting that the expected trend of net magnetic moment improvement as a function of  $\text{Mn}^{2+}$  content is only valid for normal spinel ( $i = 0$ ), with  $i$  being the inversion parameter.<sup>56–58</sup> However, the disruption of this trend has been frequently reported due to the presence of crystal defects promoted by the presence of a secondary phase such as wustite,<sup>2,3,32</sup> or the oxidation of  $\text{Mn}^{2+}$  ions to  $\text{Mn}^{3+}$  and its preference for octahedral sites.<sup>59</sup>

The enrichment of  $\text{Mn}^{2+}$  cations in the outer part of the MNPs (see Fig. 2D) could promote a configuration where the spins close to the surface are canted and barely contribute to the  $M_s$  in the static regime, explaining the unalterable  $M_s$  values with increasing  $\text{Mn}^{2+}$  content. The heterogeneous allocation of  $\text{Mn}^{2+}$  cations and the level of  $\text{Mn}^{2+}$  substitution could play a major role in reducing the average  $H_C$  and  $M_R$ . In fact, even when  $M_s$  values remained nearly constant across all samples, a slight decrease in the coercivity value ( $H_C$ ) was observed while increasing the  $\text{Mn}^{2+}$  content until  $x_{\text{Empiric}} = 0.70$ ; beyond this point, however, an opposite effect was seen for  $x_{\text{Empiric}} = 1.40$ . The reduction of  $H_C$  *via* increased  $\text{Mn}^{2+}$  substitution ultimately led to a decrease in the effective magnetic anisotropy ( $K_{\text{eff}}$ )<sup>60</sup> as also evidenced with Mössbauer

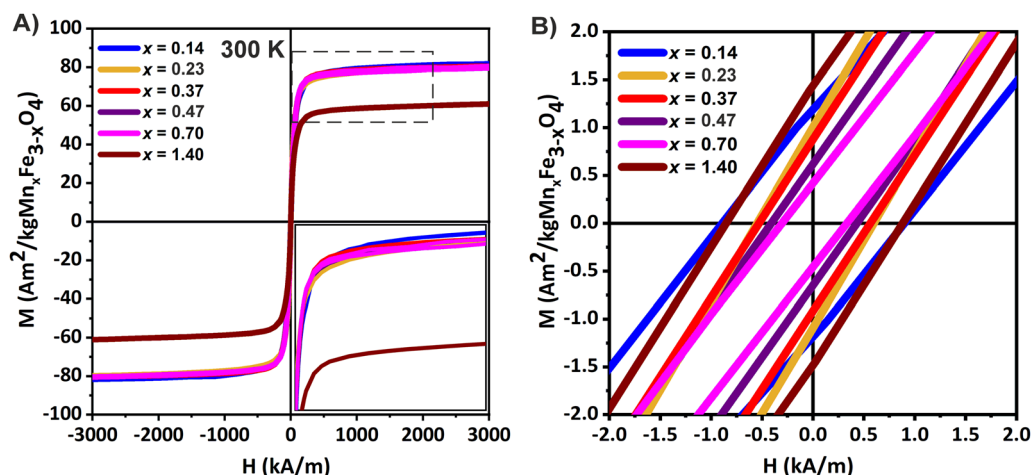


Fig. 3 (A) Static magnetization cycles recorded at 300 K for the MNPs and (B) low field region of the magnetization cycles.



measurement, indicating a transition of the MNPs towards soft magnetic behavior (Fig. 3B). An exception is the sample with the highest  $\text{Mn}^{2+}$  content ( $x_{\text{Empiric}} = 1.40$ ), where the presence of structural defects, associated with the concomitance of a reduced phase and  $\text{Mn}^{3+}$  fraction, effectively impacts their magnetic properties.

Similar results were recently reported for cobalt ferrite  $\text{Co}_x\text{Fe}_{3-x}\text{O}_4$  type MNPs, where increasing the cobalt content had little effect on  $M_s$  across samples, but led to a significant increase of  $K_{\text{eff}}$ .<sup>61</sup> In summary, considering that all samples exhibited similar average particle and crystallite sizes, and morphologies, the tuneable  $K_{\text{eff}}$ , the preference of  $\text{Mn}^{2+}$  for tetrahedral sites and the heterogeneous allocations of cations could be the key properties influencing the ultimate magnetic properties.<sup>56</sup>

### 3.5. $\text{Mn}^{2+}$ content changes after PMAO polymer coating: influence on the structural and magnetic properties

The  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs were prepared in organic solvents where they remained stabilized by an OA coating, so a subsequent transfer to the aqueous phase is required for biomedical applications. To do that, we employed a well-established polymer coating methodology, using an amphiphilic polymer, poly(maleic anhydride-*alt*-1-octadecene) (PMAO), that intercalates with the OA chains.<sup>18</sup> All MNP series were transferred to water using the same protocol, rendering MNPs stable in aqueous media for a long period of time. Table 2 summarizes the characterization of these MNPs coated with PMAO ( $\text{Mn}_x\text{@PMAO}$ ) in water. As expected, the transference into water did not affect the shape and core size of the final MNPs, as can be seen from the TEM image (Fig. 4A), and the hydrodynamic diameter measured by DLS was similar for all MNPs (Table 2). This indicates a similar transfer to water for all the MNPs regardless of the composition, allowing further comparison between the systems. The successful coating of the MNPs was additionally confirmed by TGA (Table 2), as an increase of the organic content between 10 and 24% when compared with samples only coated with OA; this is in agreement with other reported PMAO-coated MNPs.<sup>18,62</sup>

Surface modification can play a major role in the redistribution of cations, ultimately modifying the final composition of the spinel structure and its functionality.<sup>63,64</sup> To study the influence of the PMAO coating on the composition and, thus, on the structural and magnetic properties, the samples were characterized after coating by ICP-OES, FT-IR and XRD. From the ICP-OES results, we confirmed that  $\text{Mn}^{2+}$  ions leached out from the MNPs after PMAO coating (Table 2), as previously

reported after DMSA or dopamine coatings.<sup>16</sup>  $\text{Mn}^{2+}$  losses ranged from 13.0 to 21.4% of the initially incorporated amount across samples, except for the sample containing the lowest content of  $\text{Mn}^{2+}$ , which exhibited a loss of nearly 50% of its  $\text{Mn}^{2+}$  ions. This trend aligns with the XPS data (Fig. 2D).

The stability of cations occupying surface sites also depends on their interaction with the surface ligand and/or the solvent.<sup>56</sup> Fig. 4B shows the FT-IR spectra of the selected MNPs with the lowest ( $x_{\text{Empiric}} = 0.07$ ) and the highest  $\text{Mn}^{2+}$  content ( $x_{\text{Empiric}} = 1.10$ ) after PMAO coating. In region I, the signals of  $\nu(\text{C-H})$  stretching mode belonging to the OA anchored to the surface of MNPs dominate, being more intense for the sample with the highest percentage of OA ( $x_{\text{Empiric}} = 0.07$ ), as also confirmed by TGA. Next, region II is dominated by two broad bands that correspond to  $\nu_{\text{as}}(\text{COO}^-)$  and  $\nu_{\text{s}}(\text{COO}^-)$  modes of metal carboxylates, indicating the successful polymer coating. The intense band that appears in region III is characteristic of lattice Fe-O vibrations in spinel ferrites. Interestingly, as the  $\text{Mn}^{2+}$  content increased, this band showed a left shift, indicating the modification of Fe-O bond lengths and the rearrangement of the oxygen sublattice to accommodate different cation distributions among the octahedral and tetrahedral sites, which was affected by PMAO coating.<sup>56</sup> In agreement with this, a gradual shift in the mean peak (311) position can also be seen by comparing the XRD patterns of samples before and after polymer coating, while the spinel ferrite structure was maintained (Fig. 4C).

The effect of polymer coating on the magnetic properties was evaluated at 5 K and 300 K, with results summarized in Table 3. In agreement with initial oleic acid coated MNP behavior, both the  $H_C$  and the  $M_R$  decreased to near zero values at RT, indicating that the SPM regime was preserved after surface modification. The  $M_s$  values were slightly higher ( $85.0\text{--}89.0 \text{ A m}^2 \text{ kg}_{\text{ferrite}}^{-1}$ ) than those of initial MNPs (see Section 3.4 and Fig. 3) or  $\text{Fe}_3\text{O}_4$  MNPs ( $82 \text{ A m}^2 \text{ kg}^{-1}$ ) obtained under the same synthetic procedure at 300 K (Fig. 4D). Changes in the magnetic properties after surface modification have been previously reported when using different polymers such as triethyleneglycol (TEG) and polyethyleneglycol (PEG), attributed to the reduction of the spin canting effect.<sup>65,66</sup> However, this does not fully apply in our case, as the PMAO polymer is not directly coordinated to the iron ions but rather intercalated in the OA chains; nevertheless, the PMAO coating could be associated with ion leaching and subsequent cation's redistribution on the MNP surface,<sup>60,67</sup> which is relevant for applications dependent on the surface properties such as AC hysteresis and relaxometry.<sup>63</sup>

**Table 2** Summary of the physico-chemical properties of  $\text{Mn}_x\text{@PMAO}$  MNPs. Hydrodynamic radius ( $D_{\text{DLS}}$ ) is presented in terms of intensity distribution

| Samples                   | Empirical $x$ value before PMAO | Empirical $x$ value after PMAO | Measured formula                             | $D_{\text{TEM}}$ (nm $\pm$ $\sigma$ ) | $D_{\text{DLS}}$ (nm $\pm$ SD) | Z potential (mV $\pm$ SD) | Organic content (%) |
|---------------------------|---------------------------------|--------------------------------|----------------------------------------------|---------------------------------------|--------------------------------|---------------------------|---------------------|
| $\text{Mn}_x\text{@PMAO}$ | 0.14                            | 0.07                           | $\text{Mn}_{0.07}\text{Fe}_{2.93}\text{O}_4$ | $12.9 \pm 1.9$                        | $51.1 \pm 1.6$                 | $-38.1 \pm 7.2$           | 39.9                |
|                           | 0.23                            | 0.20                           | $\text{Mn}_{0.20}\text{Fe}_{2.80}\text{O}_4$ | $13.9 \pm 2.1$                        | $65.5 \pm 0.7$                 | $-37.7 \pm 6.1$           | 27.3                |
|                           | 0.37                            | 0.30                           | $\text{Mn}_{0.30}\text{Fe}_{2.70}\text{O}_4$ | $14.6 \pm 2.3$                        | $66.5 \pm 1.9$                 | $-31.2 \pm 4.8$           | 23.6                |
|                           | 0.47                            | 0.40                           | $\text{Mn}_{0.40}\text{Fe}_{2.60}\text{O}_4$ | $14.3 \pm 1.2$                        | $66.6 \pm 0.4$                 | $-39.6 \pm 8.2$           | 32.0                |
|                           | 0.70                            | 0.60                           | $\text{Mn}_{0.60}\text{Fe}_{2.40}\text{O}_4$ | $14.4 \pm 1.8$                        | $69.4 \pm 2.3$                 | $-34.3 \pm 6.8$           | 28.4                |
|                           | 1.40                            | 1.10                           | $\text{Mn}_{1.10}\text{Fe}_{1.90}\text{O}_4$ | $13.6 \pm 1.3$                        | $66.5 \pm 1.8$                 | $-32.3 \pm 4.2$           | 34.6                |



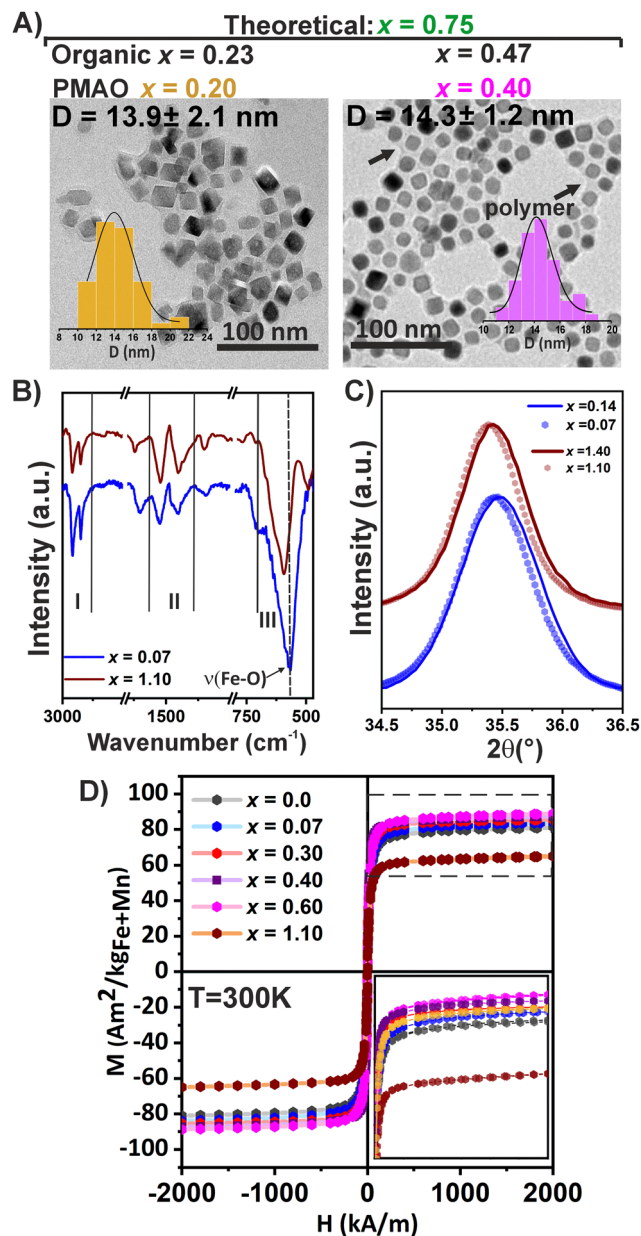


Fig. 4 Influence of the PMAO coating on the structural and magnetic properties of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs. (A) TEM images of selected  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  samples and their corresponding histogram size distribution. Theoretical and empirical  $x$  values obtained in organic and aqueous media are shown. (B) FT-IR spectra of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  with  $x_{\text{Empiric}} = 0.07$  and 1.10, respectively. (C) Comparison between XRD patterns with initial composition (organic) of  $x_{\text{Empiric}} = 0.14$ , and 1.40, and after water transference  $x_{\text{Empiric}} = 0.07$ , and 1.10, respectively. (D) Magnetization cycles of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  series ( $x_{\text{Empiric}} = 0.07$  up to 1.10) compared with  $\text{Fe}_3\text{O}_4$  ( $x = 0.0$ ) obtained using the same synthetic procedure at 300 K.

The effective anisotropy constant ( $K_{\text{eff}}$ ) values of the different MNP@PMAO samples were estimated from the formula  $K_{\text{eff}} = \frac{M_S \times H_K}{2}$ , with  $M_S$  and  $H_K$  being measured at 5 K following the Stoner and Wohlfarth model.<sup>60,68</sup> The obtained values (Table 3) confirmed a decrease in  $K_{\text{eff}}$  from 3.9 to  $2.7 \times 10^5 \text{ J m}^{-3}$  as the  $\text{Mn}^{2+}$  content increased up to  $x_{\text{Empiric}} = 0.60$  and an increase for

samples with  $x \geq 0.60$ , confirming the direct correlation between  $H_C$  and the  $\text{Mn}^{2+}$  content.  $K_{\text{eff}}$  values are approximate due to assumptions of full saturation, negligible temperature variation between 0 and 5 K, and limited interparticle interaction effects at high fields. It is noticeable that  $K_{\text{eff}}$  for  $\text{Mn}_{0.60}\text{Fe}_{2.40}\text{O}_4$  is close to the values reported for  $\text{MnFe}_2\text{O}_4$  MNPs ( $1-2 \times 10^5 \text{ J m}^{-3}$ ),<sup>60,69,70</sup> which highlights the crucial impact of the  $\text{Mn}^{2+}$  content on the effective anisotropy of the samples.

### 3.6. Tuning heating performance by changing the $\text{Mn}^{2+}$ content

The influence of the  $\text{Mn}^{2+}$  content on the heating capability of the  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs was studied by two methods: calorimetry and AC magnetometry. Low- and high-frequency measurements were conducted at magnetic and ion concentration of 2  $\text{mg}_{\text{Fe+Mn}}$  per mL or 1  $\text{mg}_{\text{Fe+Mn}}$  per mL, respectively.

**3.6.1. Calorimetric measurements.** Fig. 5A and B show the heating performance at different magnetic field intensities ranging from  $H = 3.8$  up to  $44.6 \text{ kA m}^{-1}$  under a low ( $f = 155 \text{ kHz}$ ) and a high frequency ( $f = 763 \text{ kHz}$ ), respectively. In general, samples with  $x_{\text{Empiric}} = 0.07$  up to 0.60 showed a better heating performance than the corresponding iron oxide ( $x = 0.0$ ) MNPs with similar sizes and shapes obtained under the same synthetic procedure. As expected for SPM MNPs, the SLP values increased with the intensity of the applied magnetic field and the  $\text{Mn}^{2+}$  content (until  $x_{\text{Empiric}} = 0.60$ ), being always higher under the high-frequency regime (Fig. 5B). However, for samples with  $x_{\text{Empiric}} = 1.10$ , negligible SLP values were obtained under safe clinical conditions (delimited with a red dotted line). The largest SLP value was recorded for the sample with  $x_{\text{Empiric}} = 0.60$  under both regimes, in agreement with their improved magnetic properties and low magnetic anisotropy confirmed by the previous data. The heating curve dependence of the applied frequency (155, 388, 637, and 763 kHz) under a fixed  $H = 16.8 \text{ kA m}^{-1}$  also showed a linear increase (Fig. S7 in the ESI†). One can conclude that as structural defects and the presence of  $\text{Mn}^{3+}$  species became significant ( $x_{\text{Empiric}} = 1.10$ ), a strong deterioration of  $M_S$  values was observed, and therefore, measurable heating dissipation was only possible under high magnetic field intensity exposure (Fig. 5A and B). Several works have reported the detrimental effect of crystal defects (strains, antiphase boundaries, etc.) on heat production.<sup>3,71,72</sup> This parameter is strictly linked to the synthetic protocol used for the preparation of MNPs and needs to be considered in terms of nanoheater optimization for MHT.

The SLP computed values for high and low-frequency regimes appear in Tables S6 and S7 in the ESI†. These SLP values, shown in Fig. 5A and B, were fitted with a power law  $\text{SLP} = \phi H^n$ , with  $\phi$  being the mass concentration of the MNPs in the colloid,  $H$  the amplitude of the applied field, and  $n$  the power exponent (between 1.99 and 1.09) within the linear response theory (LRT).<sup>73,74</sup> As low-frequency measurements did not produce accurate fitting, values were not considered. However, under a fixed frequency of 763 kHz (Fig. 5B), the quadratic field dependence of the SLP is fulfilled under all the range of magnetic fields tested, and it is independent of the

composition (Table S7 in the ESI†). From these data, we can conclude that the variation of the composition (maintaining a similar size and shape) with the amplitude of the magnetic field only affects the regime of dissipation of the MNPs if the incorporation of  $\text{Mn}^{2+}$  produces structural defects and/or concomitant with different Mn species like  $\text{Mn}^{3+}$ . In contrast, even with a very different  $\text{Mn}^{2+}$  content but without any impact on the average structural-magnetic properties, the heat dissipation regimen is warranted within the SPM regime. Still, the SLP values can be successfully tuned with the  $\text{Mn}^{2+}$  increase.

The magnetic relaxation process of MNPs dispersed in liquids results from individual or combination of Néel and Brown relaxation mechanisms.<sup>73,75</sup> To unveil between the predominance of Néel and Brown relaxation to produce heat over the anisotropy energy barrier, we tuned the viscosity of the medium containing the MNPs. Specifically, our best nanoheater ( $x_{\text{Empiric}} = 0.60$ ) was dispersed in water with increasing final amounts (% v/v) of glycerol (2% and 50%, viscosity range up to  $\sim 15 \text{ mPa s}^{75}$ ) and measured by calorimetry at a field intensity of  $16.8\text{--}28.8 \text{ kA m}^{-1}$  and  $f = 763 \text{ kHz}$ . We observed that the SLP values remained unaltered when the viscosity of the media was changed (see Fig. S8 in the ESI†), suggesting that the Néel relaxation process is the predominant mechanism.<sup>61,76</sup> This finding aligns with other works reporting that  $\text{Fe}_3\text{O}_4$  MNPs of 16 nm and 14 nm in water and in glycerol, respectively, are needed to maintain the predominance of Néel relaxation mechanism in a broad range of frequencies (100 kHz to 1 MHz).<sup>61,77</sup> In contrast, for more advanced compositions such as cobalt ferrite, the Néel relaxation mechanism predominates only within a size range of 6–10 nm.<sup>61,78</sup> In our case, the predominance of Néel relaxation across compositions and in the range of 13–15 nm just by controlling  $K_{\text{eff}}$  is a crucial strategy for the design of soft ferrite MNPs as heat mediators in complex environments such as tumors, where MNPs tend to aggregate, potentially compromising their magnetic properties.<sup>79–83</sup>

**3.6.2. AC magnetization measurements.** AC magnetic hysteresis loops were measured for MNPs dispersed in solutions with different  $\text{Mn}^{2+}$  contents by AC magnetometry to obtain SAR values at 150 and 300 kHz and field intensities ( $H_{\text{ac}}$ ) ranging from 4 to  $24 \text{ kA m}^{-1}$  (Fig. 5C–E). In general, the evolution of  $\text{SAR}(H_{\text{ac}})$  showed similar trends compared with the calorimetric method. As the  $\text{Mn}^{2+}$  content increased (until  $x_{\text{Empiric}} \leq 0.60$ ), the areas of the cycles increased under both frequencies at a field amplitude of  $24 \text{ kA m}^{-1}$ , while the

opposite trend was observed for samples with  $x_{\text{Empiric}} = 1.10$  (Fig. 5C and E). The evolution of the AC hysteresis loops as a function of  $H_{\text{ac}}$  (4 up to  $24 \text{ kA m}^{-1}$ ) for selected samples ( $x_{\text{Empiric}} = 0.07, 0.60$ , and  $1.10$ ) is shown in Fig. S9 in the ESI†. At 150 kHz,  $x_{\text{Empiric}} = 1.10$  displayed low SAR under all amplitudes tested, exhibiting ‘S’-shaped hysteresis loop curve characteristic of ‘hard ferrite-type’ materials,<sup>84</sup> whereas, for the rest of the samples, the heating efficiency increases quickly depending on the  $\text{Mn}^{2+}$  content consistent with the ‘soft-ferrite’ type of MNPs (Fig. 5C, D and Tables S8, S9 in the ESI†). Interestingly, field amplitude-dependent SAR appeared to be linear, with values reaching a plateau with field amplitudes above a threshold of  $\geq 20 \text{ kA m}^{-1}$  for MNPs ( $x_{\text{Empiric}} = 0.0$  up to  $0.60$ ), indicating a possible saturation (Fig. S10A in the ESI†).

Fig. 5E depicts the AC hysteresis loops at 300 kHz for samples with  $x_{\text{Empiric}} = 0.0, 0.07$ , and  $0.60$ , also showing a dependence on the  $\text{Mn}^{2+}$  content. The sample with  $x_{\text{Empiric}} = 0.60$  presented the largest opening of the AC hysteresis loops, and thus, a SAR value of about  $510 \text{ W g}_{\text{Fe+Mn}}^{-1}$ , whereas  $\text{Fe}_3\text{O}_4$  MNPs in a similar range of sizes showed a smaller area ( $\text{SAR} = 184 \text{ W g}_{\text{Fe+Mn}}^{-1}$ ) under the same AMF conditions (300 kHz,  $24 \text{ kA m}^{-1}$ ) (Fig. 5F and Table S9 in the ESI†). Linear  $\text{SAR}(H_{\text{ac}})$  dependence was maintained as in the case of 150 kHz measurement with a plateau deviation with amplitude  $\geq 20 \text{ kA m}^{-1}$  (Fig. S10B in the ESI†).

Aiming to compare both methods, we selected very near low frequencies, 155 kHz for the calorimetric method and 150 kHz for AC magnetometry at a fixed  $H$  of  $16.8 \text{ kA m}^{-1}$ . Considering our best nanoheater ( $x_{\text{Empiric}} = 0.60$ ), we obtained a  $\text{SLP} = 67.3 \text{ W g}_{\text{Fe+Mn}}^{-1}$  by calorimetry compared with  $\text{SAR} = 144.5 \text{ W g}_{\text{Fe+Mn}}^{-1}$  by magnetometry. These differences could be attributed to the non-adiabatic conditions employed for calorimetry measurements, resulting in lower  $dT/dt$  depending on the thermal exchange of MNP suspension with the surrounding media.<sup>85</sup> However, if we compare the results depicted in Fig. 5A and D it is evident that the heating capacity tendency as a function of the  $\text{Mn}^{2+}$  content is maintained in both methods, showing their complementarity.

### 3.7. MNP-cell interaction

Recently, we reported that tuning the  $\text{Mn}^{2+}$  composition is crucial to modulate the amount of reactive oxygen species (ROS) produced under MHT to enhance tissue regeneration in the invertebrate model organism *Hydra vulgaris*.<sup>86</sup> To study

Table 3 Magnetic parameters of  $\text{Mn}_x\text{@PMAO}$  samples at 300 K and 5 K

| Samples                                      | 300 K                                    |                              |                                          | 5 K                                      |                              |                                          |                                |                                              |
|----------------------------------------------|------------------------------------------|------------------------------|------------------------------------------|------------------------------------------|------------------------------|------------------------------------------|--------------------------------|----------------------------------------------|
|                                              | $M_s$ ( $\text{A m}^2 \text{ kg}^{-1}$ ) | $H_c$ ( $\text{kA m}^{-1}$ ) | $M_R$ ( $\text{A m}^2 \text{ kg}^{-1}$ ) | $M_s$ ( $\text{A m}^2 \text{ kg}^{-1}$ ) | $H_c$ ( $\text{kA m}^{-1}$ ) | $M_R$ ( $\text{A m}^2 \text{ kg}^{-1}$ ) | $H_K^a$ ( $\text{kA m}^{-1}$ ) | $K_{\text{eff}}$ ( $10^5 \text{ J m}^{-3}$ ) |
| $\text{Mn}_{0.07}\text{Fe}_{2.93}\text{O}_4$ | 85                                       | 2.6                          | 16                                       | 100                                      | 22.9                         | 40                                       | 100                            | 3.9                                          |
| $\text{Mn}_{0.30}\text{Fe}_{2.70}\text{O}_4$ | 86                                       | 2.6                          | 16                                       | 101                                      | 20.5                         | 39                                       | 80                             | 3.2                                          |
| $\text{Mn}_{0.40}\text{Fe}_{2.60}\text{O}_4$ | 87                                       | 2.6                          | 17                                       | 102                                      | 19.4                         | 37                                       | 72                             | 2.9                                          |
| $\text{Mn}_{0.60}\text{Fe}_{2.40}\text{O}_4$ | 89                                       | 2.6                          | 17                                       | 107                                      | 16.6                         | 44                                       | 64                             | 2.7                                          |
| $\text{Mn}_{1.10}\text{Fe}_{1.60}\text{O}_4$ | 66                                       | 2.6                          | 5                                        | 85                                       | 24.1                         | 18                                       | 100                            | 3.3                                          |
| $\text{Fe}_3\text{O}_4$                      | 82                                       | 2.6                          | 12                                       | 92                                       | 22.9                         | 34                                       | 80                             | 2.9                                          |

<sup>a</sup> Determined as the field at which the magnetization of the magnetized and the demagnetized branches differs in 3% of  $M_s$ .<sup>60</sup>



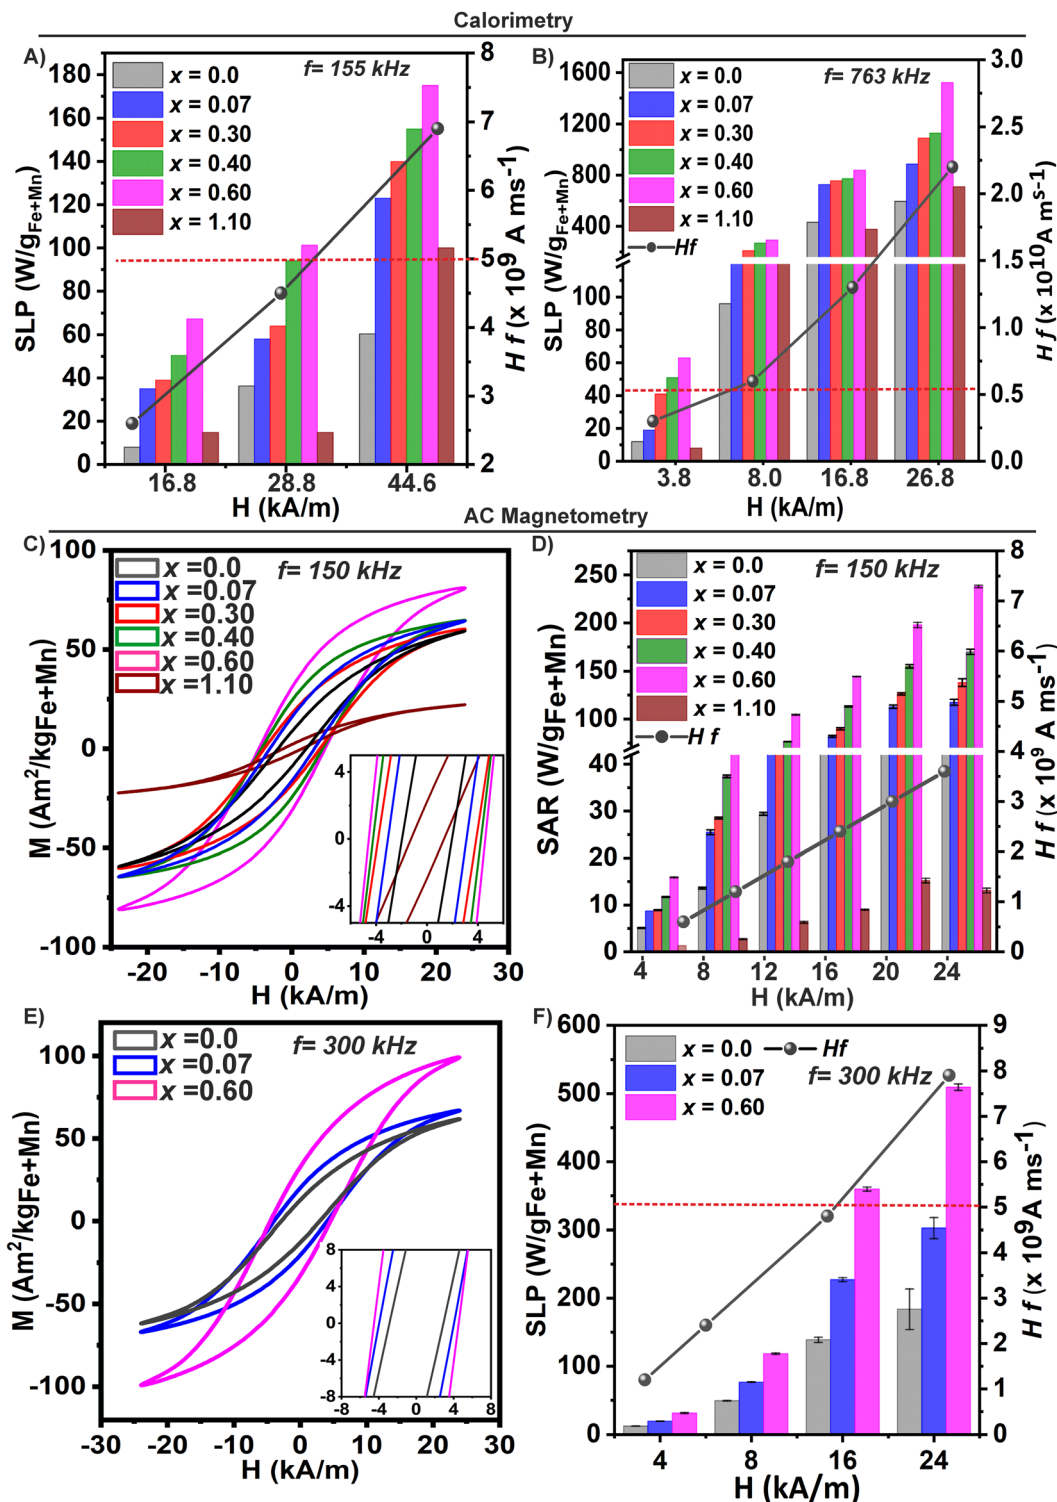


Fig. 5 Effect of the  $\text{Mn}^{2+}$  content on the heating efficiency of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs. SLP values obtained by the calorimetric method for  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs with fixed frequencies of (A)  $f = 155$  kHz and (B)  $f = 763$  kHz under field intensity ( $H$ ) ranging from 3.8 up to 44.6  $\text{kA m}^{-1}$ . (C) Dynamic magnetization curves obtained at 150 kHz and 24  $\text{kA m}^{-1}$  for samples with  $x_{\text{Empiric}} = 0.0, 0.07, 0.30, 0.40, 0.60$ , and 1.10. Inset: Magnification of the low field region. (D) SAR values of the corresponding samples (with  $x_{\text{Empiric}} = 0.0$  up to 1.10). (E) Dynamic magnetization curves obtained at 300 kHz and 24  $\text{kA m}^{-1}$  of samples with  $x_{\text{Empiric}} = 0.07$  and 0.70, respectively, compared to samples without  $\text{Mn}^{2+}$  ( $x = 0.0$ ). Inset: Low field region. (F) SAR value of samples measured in (E). Black dots represent the  $Hf$  values for each condition tested. Safe clinic  $Hf$  values are delimited with a red dotted line.

the future potential of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs for cancer treatment, we selected two MNPs with different heating capacities ( $x_{\text{Empiric}} =$

0.07 and 0.60). To confer improved stability in biological media and target tumoral cells, the samples were functionalized with



glucose molecules.<sup>19</sup> The cytotoxicity of  $\text{Mn}_{0.07}\text{Fe}_{2.93}\text{O}_4$  and  $\text{Mn}_{0.60}\text{Fe}_{2.40}\text{O}_4$  MNPs functionalized with glucose at different concentrations (ranging from 0 to  $150\ \mu\text{g mL}^{-1}$ ) was evaluated by MTT assay, a well-known colorimetric method used to assess cell metabolic activity as an indicator of cell viability. Cell viability of the MIA PaCa-2 cell line was greater than 90% for both systems ( $x_{\text{Empiric}} = 0.07$  and  $0.60$ , respectively) after 24 h of treatment, suggesting the absence of cell cytotoxicity and the biocompatibility of MNPs up to  $150\ \mu\text{g mL}^{-1}$  (Fig. 6A and B). These results are consistent with previously published data where low levels of toxicity are reported in different cell lines for manganese iron oxide nanoparticles.<sup>16,87,88</sup> Similarly, these results mirror those obtained *in vivo* in *Hydra vulgaris*, where none of the both MNPs resulted toxic.<sup>86</sup>

Then, we assessed the internalization of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  in the MIA PaCa-2 cell line by fluorescence microscopy. As can be seen in Fig. 6C, large amounts of both  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs appeared internalized inside the cells as red spots in comparison with the control (cells without MNPs), suggesting high cellular uptake after 24 h of treatment. This result is important for applications like classical magnetic hyperthermia where high internalization of iron is required to achieve therapeutic heat. To confirm that, the intracellular iron content was measured by ICP-OES. After 24 h of treatment, the amount of intracellular Fe was 8 and 15 pg per cell for  $\text{Mn}_{0.07}\text{Fe}_{2.93}\text{O}_4$  and  $\text{Mn}_{0.60}\text{Fe}_{2.40}\text{O}_4$  MNPs, respectively. The different uptake between samples could be

attributed to a different amount of glucose functionalized on the MNP surface, or to a diverse stability in biological media. Further studies to elucidate the dependence between MNPs composition and cellular internalization are still needed.

## 4. Conclusions

Besides the shape and size, the composition of MNPs is a critical parameter to tune heating efficiency. In this study, we investigated the effects of the manganese content on the structural, magnetic and heating response of  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs before and after water transference. Our study reveals a compositional gradient in the Mn/Fe atomic ratios across the MNPs, with the surface layers being enriched in  $\text{Mn}^{2+}$  relative to the deeper core regions. This heterogeneity becomes more pronounced as the  $\text{Mn}^{2+}$  substitution level decreases. The data suggest that Mn ions primarily incorporate into the ferrite structure starting from the outermost layers, gradually extending toward the interior of the nanoparticles. The surface of the nanoparticles, enriched with  $\text{Mn}^{2+}$ , likely exhibits a SPM relaxation, while the inner core remains predominantly FiM. We have successfully tuned the  $K_{\text{eff}}$  by varying the  $\text{Mn}^{2+}$  content in the samples with  $x_{\text{Empiric}} \leq 0.70$  while keeping the  $M_s$  and crystallite sizes relatively constant. In contrast, a higher  $\text{Mn}^{2+}$  content ( $x_{\text{Empiric}} = 1.40$ ) exhibited additional secondary crystalline

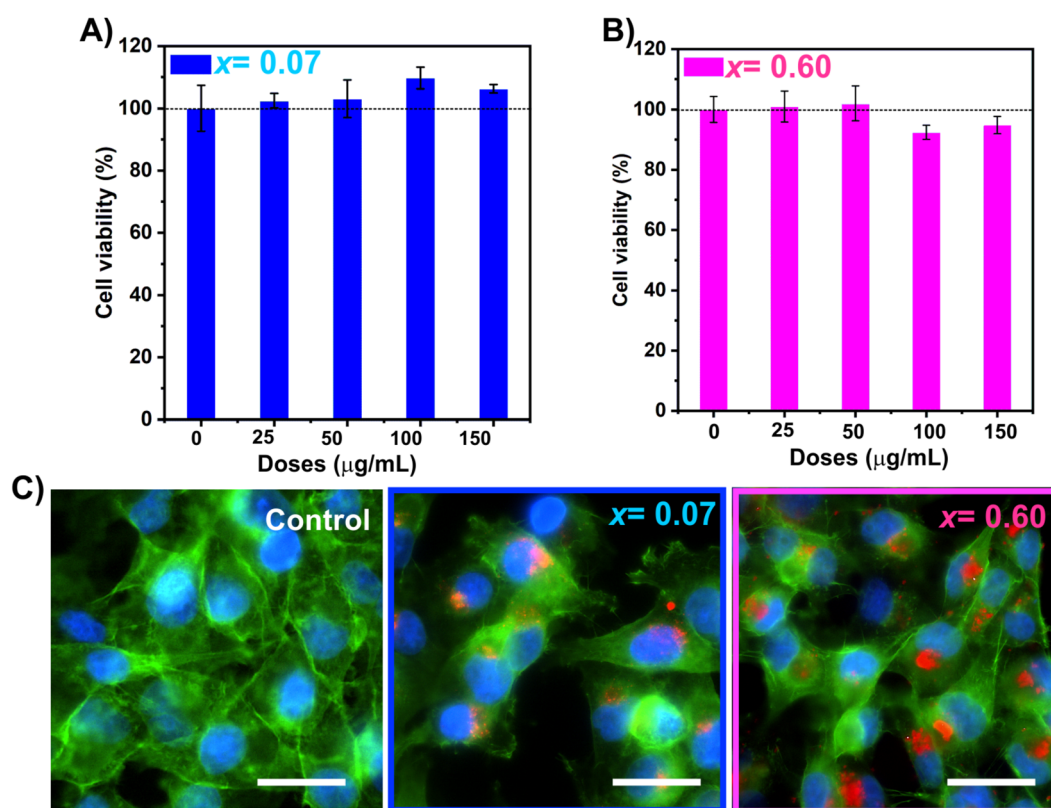


Fig. 6 (A) and (B) Viability assay of the MIA PaCa-2 cell line loaded  $\text{Mn}_x\text{Fe}_{3-x}\text{O}_4$  MNPs, with  $x = 0.07$  and  $0.60$ , respectively. (C) Fluorescence images taken after 24 h of incubation with  $100\ \mu\text{g mL}^{-1}$  of TAMRA-labelled MNPs in MIA PaCa-2 cells. Nuclei (blue), F-actin (green) and MNPs (red). Scale bar =  $20\ \mu\text{m}$ .



phase, strain defects, and the presence of  $\text{Mn}^{3+}$  species, affecting the  $M_s$  values although the final crystallite size also remained unalterable. Water transference by PMAO coating caused ion leaching that clearly changed the initial composition of the MNPs, but average static magnetic properties were maintained. The heating efficiency was effectively tuned by changing the  $\text{Mn}^{2+}$  content, being the ferrite with  $x_{\text{Empiric}} = 0.60$  the one with the optimal  $\text{Mn}^{2+}$  concentration and anisotropy that maximize SLP. The Néel relaxation process was the predominant mechanism to produce heat for our set of MNPs. Importantly, cell viability remained greater than 90% for the  $\text{Mn}^{2+}$  tested concentration, suggesting that this system is safe after 24 hours of treatment. Essentially, our study highlights the importance of fine-tuning these properties and presents a valuable framework for advancing magnetic hyperthermia through targeted nanoparticle design. Moreover, the ability to control magnetic anisotropy and heating performance through the  $\text{Mn}^{2+}$  content highlights the potential of these nanoparticles for biomedical applications, including localized *in vivo* hyperthermia treatments, as recently demonstrated in *Hydra vulgaris*.<sup>86</sup>

## Author contributions

O. F. O.: investigation, XPS measurement and analysis, data curation, and writing – original draft. G. T.: investigation, biological experiment, data curation, and writing – original draft. F. J. T.: resources and review and editing. J. G. O.: investigation and review and editing. J. R.: Mossbauer measurement and analysis and writing – original draft. M. M.: conceptualization, funding acquisition, project administration, supervision and review and editing. S. D.S. F.: conceptualization, investigation, data curation, formal analysis, writing – original draft and review and editing.

## Conflicts of interest

There are no conflicts to declare.

## Data availability

The data supporting this article have been included as part of the ESI.†

## Acknowledgements

S. D.S.-F. acknowledges Marie Skłodowska-Curie Postdoctoral Fellowships (HORIZON-MSCA-2021-PF-01-01, Grant agreement No. 101064735) funded by the European Union. This work has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation program (Grant agreement No. 853468), MCIN/AEI/10.13039/501100011033 and FSE+ (PID2021-122508NB-I00) and project CNS2022-135700 funded by MICIU/AEI/10.13039/501100011033 and the European Union NextGenerationEU/

PRTR. The authors would like to acknowledge Fondo Social del Gobierno de Aragón (grupo DGA E15\_23R) and MCIN with funding from European Union NextGenerationEU (PRTR-C17.I1) promoted by the Government of Aragon and CEX2023-001286-S funding from MICIU/AEI/10.13039/501100011033. The project CONAHCyT LNC-2023-95 partially supported this study. The authors would like to acknowledge the use of Advanced Microscopy Laboratory (Universidad de Zaragoza), for access to their instrumentation and expertise and the use of Servicio General de Apoyo a la Investigación-SAI, Universidad de Zaragoza. Likewise, the authors thank LNCAE (Laboratorio Nacional de Conversión y Almacenamiento de Energía) of the IPN (Instituto Politécnico Nacional) for access to its XPS experimental facility. We also thank Professor M. del Puerto Morales (MaMBIO Group, ICMM), Professor Edilso Reguera (CICATA-Legaria, IPN) and Dr. Raluca Fratila (Bionanosurf group, INMA-CSIC).

## References

- H. Gavilán, S. K. Avugadda, T. Fernández-Cabada, N. Soni, M. Cassani, B. T. Mai, R. Chantrell and T. Pellegrino, *Chem. Soc. Rev.*, 2021, **50**, 11614–11667.
- L. Yang, L. Ma, J. Xin, A. Li, C. Sun, R. Wei, B. W. Ren, Z. Chen, H. Lin and J. Gao, *Chem. Mater.*, 2017, **29**, 3038–3047.
- S. Del Sol Fernández, O. F. Odio, P. M. Crespo, E. O. Pérez, G. Salas, L. Gutiérrez, M. del P. Morales and E. Reguera, *J. Phys. Chem. C*, 2022, **126**, 10110–10128.
- S. S. Phalake, M. S. Lad, K. V. Kadam, S. A. M. Tofail, N. D. Thorat and V. M. Khot, *ACS Omega*, 2022, **7**, 44187–44198.
- D. Li, H. Yun, B. T. Diroll, V. V. T. Doan-Nguyen, J. M. Kikkawa and C. B. Murray, *Chem. Mater.*, 2016, **28**, 480–489.
- N. Zufelato, V. R. R. Aquino, N. Shrivastava, S. Mendanha, R. Miotto and A. F. Bakuzis, *ACS Appl. Nano Mater.*, 2022, **5**, 7521–7539.
- X. Lasheras, M. Insausti, J. M. de la Fuente, I. G. de Muro, I. Castellanos-Rubio, L. Marciano, M. L. Fernández-Gubieda, A. Serrano, R. Martín-Rodríguez and E. Garaio, *et al.*, *Dalton Trans.*, 2019, **48**, 11480–11491.
- Z. Yan, A. Chaluvadi, S. FitzGerald, S. Spence, C. Bleyer, J. Zhu, T. M. Crawford, R. B. Getman, J. Watt and D. L. Huber, *et al.*, *Nanoscale Adv.*, 2022, **4**, 3957–3965.
- A. Doaga, A. M. Cojocariu, W. Amin, F. Heib, P. Bender, R. Hempelmann and O. F. Caltun, *Mater. Chem. Phys.*, 2013, **143**, 305–310.
- L. T. Lu, N. T. Dung, L. D. Tung, C. T. Thanh, O. K. Quy, N. V. Chuc, S. Maenosono and N. T. K. Thanh, *Nanoscale*, 2015, **7**, 19596–19610.
- X. Yu, T. Yang, C. Lv, L. Wang, R. Liu, D. Tian and S. He, *et al.*, *J. Alloys Compd.*, 2023, **937**, 168291.
- D. Li, H. Yun, B. T. Diroll, V. V. T. Doan-Nguyen, J. M. Kikkawa and C. B. Murray, *Chem. Mater.*, 2016, **28**, 480–489.
- Z. Yan, A. Chaluvadi, S. FitzGerald, S. Spence, C. Bleyer, J. Zhu, T. M. Crawford, R. B. Getman, J. Watt and D. L. Huber, *et al.*, *Nanoscale Adv.*, 2022, **4**, 3957–3965.



- 14 R. Otero-Lorenzo, E. Fantechi, C. Sangregorio and V. Salgueiriño, *Chem. – Eur. J.*, 2016, **22**, 6666–6675.
- 15 L. H. Nguyen, N. X. Phuc, D. H. Manh, N. H. Nam, N. X. Truong, N. V. Quynh, P. T. Phong and P. H. Nam, *J. Electron. Mater.*, 2021, **50**, 5318–5326.
- 16 D. Garcia-Soriano, R. Amaro, N. Lafuente-Gómez, P. Milán-Rois, Á. Somoza, C. Navio, F. Herranz, L. Gutiérrez and G. Salas, *J. Colloid Interface Sci.*, 2020, **578**, 510–521.
- 17 H. Zeng, P. M. Rice, S. X. Wang and S. Sun, *J. Am. Chem. Soc.*, 2004, **126**, 11458–11459.
- 18 M. Moros, B. Pelaz, P. López-Larrubia, M. L. Garcia-Martin, V. Grazú and J. M. de La Fuente, *Nanoscale*, 2010, **2**, 1746–1755.
- 19 M. Moros, B. Hernaez, E. Garet, J. T. Dias, B. Saez, V. Grazu, A. Gonzalez-Fernandez, C. Alonso and J. M. de la Fuente, *ACS Nano*, 2012, **6**, 1565–1577.
- 20 K. R. Desai, S. T. Alone, S. R. Wadgane, S. E. Shirsath, K. M. Batoo, A. Imran, E. H. Raslan, M. Hadi, M. F. Ijaz and R. H. Kadam, *Phys. B*, 2021, **614**, 413054.
- 21 J. T. Dias, M. Moros, P. Del Pino, S. Rivera, V. Grazú and J. M. de la Fuente, *Angew. Chem.*, 2013, **125**, 11740–11743.
- 22 B. Mehdaoui, J. Carrey, M. Stadler, A. Cornejo, C. Nayral, F. Delpech, B. Chaudret and M. Respaud, *Appl. Phys. Lett.*, 2012, **100**(5), 052403.
- 23 G. Cotin, F. Pertont, C. Petit, S. Sall, C. Kiefer, V. Begin, B. Pichon, C. Lefevre, D. Mertz and J.-M. Greneche, *et al.*, *Chem. Mater.*, 2020, **32**, 9245–9259.
- 24 W. Baaziz, B. P. Pichon, S. Fleutot, Y. Liu, C. Lefevre, J.-M. Greneche, M. Toumi, T. Mhiri and S. Begin-Colin, *J. Phys. Chem. C*, 2014, **118**, 3795–3810.
- 25 C. Moya, X. Batlle and A. Labarta, *Phys. Chem. Chem. Phys.*, 2015, **17**, 27373–27379.
- 26 Q. Song, Y. Ding, Z. L. Wang and Z. J. Zhang, *Chem. Mater.*, 2007, **19**, 4633–4638.
- 27 F. J. Douglas, D. A. MacLaren and M. Murrie, *RSC Adv.*, 2012, **2**, 8027–8035.
- 28 S. Carregal-Romero, A. B. Miguel-Coello, L. Martínez-Parra, Y. Martí-Mateo, P. Hernansanz-Agustín, Y. Fernández-Afonso, S. Plaza-García, L. Gutiérrez, M. d. M. Muñoz-Hernández, J. Carrillo-Romero, M. Piñol-Cancer, P. Lecante, Z. Blasco-Iturri, L. Fadón, A. C. Almansa-García, M. Möller, D. Otaegui, J. A. Enríquez, H. Groult and J. Ruiz-Cabello, *Ultrasmall Manganese Ferrites for In Vivo Catalase Mimicking Activity and Multimodal Bioimaging*, *Small*, 2022, **18**, 2106570.
- 29 S. D. Oberdick, A. Abdelgawad, C. Moya, S. Mesbahi-Vasey, D. Kepaptsoglou, V. K. Lazarov, R. F. L. Evans, D. Meilak, E. Skoropata and J. van Lierop, *et al.*, *Sci. Rep.*, 2018, **8**, 1–12.
- 30 A. Ullrich, M. M. Rahman, P. Longo and S. Horn, *Sci. Rep.*, 2019, **9**, 1–9.
- 31 A. Lak, D. Niculaes, G. C. Anyfantis, G. Bertoni, M. J. Barthel, S. Marras, M. Cassani, S. Nitti, A. Athanassiou and C. Giannini, *et al.*, *Sci. Rep.*, 2016, **6**, 33295.
- 32 A. Lak, M. Cassani, B. T. Mai, N. Winckelmans, D. Cabrera, E. Sadrollahi, S. Marras, H. Remmer, S. Fiorito and L. Cremades-Jimeno, *et al.*, *Nano Lett.*, 2018, **18**, 6856–6866.
- 33 G. K. Williamson and W. H. Hall, *Acta metallurgica*, 1953, **1**, 22–31.
- 34 P. Monisha, P. Priyadharshini, S. S. Gomathi and K. Pushpanathan, *J. Phys. Chem. Solids*, 2021, **148**, 109654.
- 35 C. S. Fadley, D. A. Shirley, A. J. Freeman, P. S. Bagus and J. V. Mallow, *Phys. Rev. Lett.*, 1969, **23**, 1397–1401.
- 36 S. Hüfner and G. K. Wertheim, *Phys. Rev. B*, 1973, **7**, 2333–2336.
- 37 G.-H. Gweon and J.-G. S.-J. Park, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 1993, **48**, 7825–7835.
- 38 R. Gupta and D. Sharma, *ACS Appl. Nano Mater.*, 2020, **3**, 2026–2037.
- 39 I. V. Chernyshova, S. Ponnuramgam and P. Somasundaran, *J. Am. Chem. Soc.*, 2011, **133**, 9536–9544.
- 40 J. F. van Acker, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 1988, **37**, 6827–6834.
- 41 J. C. Carver, G. K. Schweitzer and T. A. Carlson, *J. Chem. Phys.*, 1972, **57**, 973–982.
- 42 V. R. Galakhov, M. Demeter, S. Bartkowski, M. Neumann, N. A. Ovechkina, E. Z. Kurmaev, N. I. Lobachevskaya, Y. M. Mukovskii, J. Mitchell and D. L. Ederer, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 2002, **65**, 113102.
- 43 G. C. Allen, S. J. Harris, J. A. Jutson and J. M. Dyke, *Appl. Surf. Sci.*, 1989, **37**, 111–134.
- 44 A. Kumar, B. N. Mahanty, A. Rawat, R. Muhammad, R. K. Panigrahi, D. Pradhan and P. Mohanty, *Energy Fuels*, 2023, **37**, 6810–6823.
- 45 S. Güner, A. Baykal, M. Amir, H. Güngüneş, M. Geleri, H. Sözeri, S. E. Shirsath and M. Sertkol, *J. Alloys Compd.*, 2016, **688**, 675–686.
- 46 J. B. Goodenough, *Phys. Rev. B*, 1955, **100**, 564–573.
- 47 E.-K. Viinikka and Y. Öhrn, *Phys. Rev. B:Condens. Matter Mater. Phys.*, 2002, **65**, 113102.
- 48 S. Tanuma, C. J. Powell and D. R. Penn, *Surf. Interface Anal.*, 1991, **17**, 911–926.
- 49 P. P. Bakare, M. P. Gupta, S. K. Date and A. P. B. Sinha, *Proc. Indiana Acad. Sci. – Chem. Sci.*, 1984, **93**, 1349–1359.
- 50 K. S. Al-Rashdi, H. M. Widatallah, F. Al Mari, O. Cespedes, M. Elzain, A. Al-Rawas, A. Gismelseed and A. Yousif, *Hyperfine Interact.*, 2018, **239**, 1–11.
- 51 G. A. Sawatzky, F. Van Der Woude and A. H. Morrish, *Phys. Rev.*, 1969, **187**, 747–757.
- 52 F. L. Deepak, M. Bañobre-López, E. Carbó-Argibay, M. F. Cerqueira, Y. Piñero-Redondo, J. Rivas, C. M. Thompson, S. Kamali, C. Rodríguez-Abreu, K. Kovnir and Y. V. Kolen'ko, *J. Phys. Chem. C*, 2015, **119**, 11947–11957.
- 53 D. G. Rancourt and J. Y. Ping, *Nucl. Instrum. Methods Phys. Res., Sect. B*, 1991, **58**, 85–97.
- 54 R. Gerber and G. Elbinger, *J. Phys. C: Solid State Phys.*, 1970, **3**, 1363.
- 55 A. Broese Van Groenou, J. A. Schulkes and D. A. Annis, *J. Appl. Phys.*, 1967, 1133–1134.
- 56 K. R. Sanchez-Lievanos, J. L. Stair and K. E. Knowles, *Inorg. Chem.*, 2021, **60**, 4291–4305.
- 57 K. M. Noh, Y. B. Lee, W. H. Kwon, J. Y. Kang, W.-O. Choi and K. P. Chae, *J. Magn.*, 2016, **21**, 308–314.



- 58 R. A. McCurrie, *Mater. Manuf. Processes*, 1995, **10**, 1300–1301.
- 59 X. Lasheras, M. Insausti, J. M. de la Fuente, I. G. de Muro, I. Castellanos-Rubio, L. Marcano, M. L. Fernández-Gubieda, A. Serrano, R. Martín-Rodríguez and E. Garaio, *et al.*, *Dalton Trans.*, 2019, **48**, 11480–11491.
- 60 B. Aslibeiki, P. Kameli and H. Salamati, *J. Appl. Phys.*, 2016, **119**, 63901.
- 61 A. A. de Almeida, F. Fabris, G. S. da Silva, K. R. Pirota, M. Knobel and D. Muraca, *ACS Appl. Mater. Interfaces*, 2025, **17**, 13083–13093.
- 62 O. K. Arriortua, M. Insausti, L. Lezama, I. G. de Muro, E. Garaio, J. M. de la Fuente, R. M. Fratila, M. P. Morales, R. Costa and M. Eceiza, *et al.*, *Colloids Surf., B*, 2018, **165**, 315–324.
- 63 E. A. Schultz-Sikma, H. M. Joshi, Q. Ma, K. W. MacRenaris, A. L. Eckermann, V. P. Dravid and T. J. Meade, *Chem. Mater.*, 2011, **23**, 2657–2664.
- 64 H. Ma, L. Guo, H. Zhang, Y. Wang, Y. Miao, X. Liu, M. Peng, X. Deng, Y. Peng and H. Fan, *ACS Appl. Bio Mater.*, 2022, **5**, 3067–3074.
- 65 B. Aslibeiki, P. Kameli, M. H. Ehsani, H. Salamati, G. Muscas, E. Agostinelli, V. Foglietti, S. Casciardi and D. Peddis, *J. Magn. Magn. Mater.*, 2016, **399**, 236–244.
- 66 D. E. Zhang, X. J. Zhang, X. M. Ni, H. G. Zheng and D. D. Yang, *J. Magn. Magn. Mater.*, 2005, **292**, 79–82.
- 67 P. Guardia, B. Batlle-Brugal, A. G. Roca, O. Iglesias, M. D. P. Morales, C. J. Serna, A. Labarta and X. Batlle, *J. Magn. Magn. Mater.*, 2007, **316**, e756–e759.
- 68 E. C. Stoner and E. P. Wohlfarth, *Philos. Trans. R. Soc., A*, 1948, **240**, 599–642.
- 69 D. Carta, M. F. Casula, A. Falqui, D. Loche, G. Mountjoy, C. Sangregorio and A. Corrias, *J. Phys. Chem. C*, 2009, **113**, 8606–8615.
- 70 S. Yoon and K. M. Krishnan, *J. Appl. Phys.*, 2011, **109**, 07B534.
- 71 M. Levy, A. Quarta, A. Espinosa, A. Figuerola, C. Wilhelm, M. García-Hernández, A. Genovese, A. Falqui, D. Alloyeau, R. Buonsanti, P. D. Cozzoli, M. A. García, F. Gazeau and T. Pellegrino, *Chem. Mater.*, 2011, **23**, 4170–4180.
- 72 S. Kubickova, D. Niznansky, M. P. Morales Herrero, G. Salas and J. Vejpravova, *Appl. Phys. Lett.*, 2014, **104**, 223105.
- 73 J. Carrey, B. Mehdaoui and M. Respaud, *J. Appl. Phys.*, 2011, **109**, 83921.
- 74 T. E. Torres, E. Lima Jr, M. P. Calatayud, B. Sanz, A. Ibarra, R. Fernández-Pacheco, A. Mayoral, C. Marquina, M. R. Ibarra and G. F. Goya, *Sci. Rep.*, 2019, **9**, 3992.
- 75 D. Cabrera, A. Lak, T. Yoshida, M. E. Materia, D. Ortega, F. Ludwig, P. Guardia, A. Sathya, T. Pellegrino and F. J. Teran, *Nanoscale*, 2017, **9**, 5094–5101.
- 76 I. Castellanos-Rubio, I. Rodrigo, A. Olazagoitia-Garmendia, O. Arriortua, I. de Muro, J. S. Garitaonandia, J. R. Bilbao, M. L. Fdez-Gubieda, F. Plazaola and I. Aki Orue, *et al.*, *ACS Appl. Mater. Interfaces*, 2020, **12**, 27917–27929.
- 77 J.-P. Fortin, C. Wilhelm, J. Servais, C. Ménager, J.-C. Bacri and F. Gazeau, *J. Am. Chem. Soc.*, 2007, **129**, 2628–2635.
- 78 B. Mehdaoui, A. Meffre, J. Carrey, S. Lachaize, L.-M. Lacroix, M. Gougeon, B. Chaudret and M. Respaud, *Adv. Funct. Mater.*, 2011, **21**, 4573–4581.
- 79 A. Lak, M. Cassani, B. T. Mai, N. Winckelmans, D. Cabrera, E. Sadrollahi, S. Marras, H. Remmer, S. Fiorito and L. Cremades-Jimeno, *et al.*, *Nano Lett.*, 2018, **18**, 6856–6866.
- 80 D. Cabrera, A. Coene, J. Leliaert, E. J. Artés-Ibáñez, L. Dupré, N. D. Telling and F. J. Teran, *ACS Nano*, 2018, **12**, 2741–2752.
- 81 D. Cabrera, A. Lak, T. Yoshida, M. E. Materia, D. Ortega, F. Ludwig, P. Guardia, A. Sathya, T. Pellegrino and F. J. Teran, *Nanoscale*, 2017, **9**, 5094–5101.
- 82 R. Di Corato, A. Espinosa, L. Lartigue, M. Tharaud, S. Chat, T. Pellegrino, C. Ménager, F. Gazeau and C. Wilhelm, *Biomaterials*, 2014, **35**, 6400–6411.
- 83 P. T. Phong, L. H. Nguyen, L. T. H. Phong, P. H. Nam, D. H. Manh, I. J. Lee and N. X. Phuc, *J. Magn. Magn. Mater.*, 2017, **428**, 36–42.
- 84 F. Soetaert, S. K. Kandala, A. Bakuzis and R. Ivkov, *Sci. Rep.*, 2017, **7**, 6661.
- 85 R. M. Fratila and J. M. De La Fuente, *Nanomaterials for magnetic and optical hyperthermia applications*, Elsevier, 2018.
- 86 G. Tommasini, S. Del Sol-Fernández, A. C. Flavián-Lázaro, A. Lewinska, M. Wnuk, C. Tortiglione and M. Moros, *Adv. Funct. Mater.*, 2024, **34**, 2405282.
- 87 S. Del Sol-Fernández, Y. Portilla-Tundidor, L. Gutiérrez, O. F. Odio, E. Reguera, D. F. Barber and M. P. Morales, *ACS Appl. Mater. Interfaces*, 2019, **11**, 26648–26663.
- 88 D. García-Soriano, P. Milán-Rois, N. Lafuente-Gómez, C. Navio, L. Gutiérrez, L. Cussó, M. Desco, D. Calle, Á. Somoza and G. Salas, *J. Colloid Interface Sci.*, 2022, **613**, 447–460.

