





 Cite this: *RSC Adv.*, 2025, **15**, 26276

Utilization of natural and waste sources for synthesis of cellulose, chitin, and chitosan for a suitable environment

 Bipul Mondal Sagar,^a Md. Mozahidul Islam,^b Md. Lawshan Habib,^c *^a
 Samina Ahmed *^c and Md. Sahadat Hossain *^c

The growing need for sustainable materials has sparked interest in natural polymers such as cellulose, chitin, and chitosan. This review explored the synthesis routes and various natural and waste-derived sources of these biopolymers. Chitin and chitosan, obtained primarily from crustaceans, insects, and microorganisms, are economically valuable due to their biodegradability and biocompatibility. Chitosan is produced through demineralization, deproteinization, and deacetylation using either chemical methods or microbial fermentation. Cellulose is extracted from agro-waste (e.g., banana peels, rice husks) and textile residues using chemical or mechanical techniques, with processing occurring on nano to macro scales through pre-hydrolysis, bleaching, and pulping. Emphasizing synthesis conditions, environmental implications, and industrial relevance, this review aims to comprehensively understand these polymers' structural characteristics and processing pathways, offering guidance for future research and sustainable waste valorization.

 Received 25th April 2025
 Accepted 12th July 2025

DOI: 10.1039/d5ra02896e

rsc.li/rsc-advances

1. Introduction

As environmental pollution and climate change escalate, sustainable waste management is crucial. Researchers are developing eco-friendly materials to minimize ecological harm and enhance resource efficiency.^{1,2} Every year, the seafood processing industry generates millions of tons of shell debris, which includes waste from shrimp, lobster, and crabs. The EU handles more than 100 000 MT of shell trash, but India alone produces up to 80 000 MT.³ The large volume of waste is difficult for the seafood industry to manage, and they are frequently viewed as an environmental burden. Landfills, incineration, and ocean dumping are examples of disposal techniques that harm ecosystems, cause climate change, and deplete oxygen. Biological decline, ocean acidification, and widespread coral siltation are further environmental problems.⁴⁻⁶ Because of its non-toxic, biodegradable, and biocompatible qualities, seafood waste, which is abundant in polysaccharides like chitin and its derivative chitosan, has enormous potential.^{6,7} Chitin is a white, harsh, rigid, and nitrogenous substance regarded as a regenerative raw

material.⁸ The second most abundant polymer after cellulose, chitin is present in the exoskeletons of arthropods, yeast, and marine life.^{6,9} Chitins are also mostly found in the exoskeletons of insects, mollusks, fungi, and annelids.¹⁰ Its yearly biological output is estimated to be between 10¹⁰ and 10¹² tons worldwide. Seafood waste is still mostly dumped in landfills or the ocean, causing pollution despite its commercial potential.³

Waste textiles, consisting of cellulose, are plentiful but mostly unused. In 2020, 109 million tons of fiber were produced worldwide, with 36% of that amount coming from plant and synthetic cellulosic fibers. The largest portion, 26.2 million tons, was comprised of cotton. Only 14% of post-consumer apparel was recycled in 2017, despite the possibility of recycling; the majority ended up in landfills or incinerators.¹¹ In 2010, 75.5 million tons of textile fibers were needed, and by 2030, that number is predicted to rise to 133.5 million tons.¹² The accumulation of textile waste in landfills favors the spread of diseases and contributes to greenhouse gas emissions.¹³ European households generated over 200 million tons of waste in 2014. Despite recycling systems, much paper waste ends up in mixed municipal solid waste (MSW). The EU set targets for 55% MSW recycling by 2025 and 65% by 2035, aiming to reduce landfilling and enhance sustainability through stricter packaging waste rules.¹⁴

The primary component of plant cell walls, cellulose, keeps plants rigid and straight. The first source of cellulose was plants. The French chemist Anselme Payen used plants as a source of cellulose. He extracted cellulose from plants and determined its chemical formula in 1838.¹⁵ Based on size, cellulose can be divided into two categories: microcellulose and

^aDepartment of Applied Chemistry and Chemical Engineering, Gopalganj Science and Technology University, Gopalganj, Bangladesh. E-mail: lawshanhabibsh20@gmail.com

^bDepartment of Applied Chemistry and Chemical Engineering, Noakhali Science and Technology University, Noakhali, Bangladesh

^cInstitute of Glass and Ceramic Research and Testing, Bangladesh Council of Scientific and Industrial Research (BCSIR), Dhaka-1205, Bangladesh. E-mail: shanta_samina@yahoo.com; saz8455@gamil.com



nanocellulose.¹⁶ Nanocellulose (at least one dimension ≤ 100 nm) is further subdivided into three principal types: bacterial nanocellulose (BNC), nanocrystalline cellulose (NCC or CNC), and nano- or micro-fibrillated cellulose (NFC or MFC).^{17,18} BNC is biosynthesized by certain bacterial species, such as *Komagataeibacter xylinus*, and is known for its exceptional purity, high crystallinity, and three-dimensional nanofiber network, making it ideal for biomedical applications due to its outstanding biocompatibility and mechanical strength.¹⁹ NCC is obtained through acid hydrolysis of cellulose fibers, producing rod-shaped, highly crystalline particles typically 100–500 nm in length and 5–20 nm in width.²⁰ In contrast, NFC consists of long, flexible fibrils containing both crystalline and amorphous domains. It is produced *via* mechanical shearing, often assisted by enzymatic or chemical pretreatments. It is characterized by high viscosity, water-holding capacity, and potential applications in coatings, packaging, and biocomposites.²¹

There are three methods to extract cellulose: mechanical, chemical, and bacterial methods. Among the mechanical cellulose extraction techniques are steam explosion, crushing, grinding, and high-pressure homogenization. Alkali treatment, chemical retting, degumming, and acid retting are examples of chemical extraction techniques.²² Cellulose can also be extracted from rice husk,²³ rice straw,²⁴ sugarcane bagasse,²⁵ cotton stalk,²⁶ sisal fiber,²⁷ mengkuang leaves,²⁸ kenaf,²⁹ jute,³⁰ coconut coil,³¹ pineapple crown leaves,³² pineapple leaves,³³ banana peel,³⁴ alfa grass,³⁵ municipal grass,³⁶ Native African Napier grass,³⁷ sabai grass,³⁸ bamboo,³⁹ barks of mulberry,⁴⁰ wheat straw,⁴¹ corncob,⁴² poplar trees wood,⁴³ soybean,⁴⁴ lemon peel,⁴⁵ jackfruit peel,⁴⁶ Palm oil empty fruit bunches,⁴⁷ carrot peel,⁴⁸ onion peel,⁴⁹ pumpkin peel,⁵⁰ tomato peel,⁵¹ potato residues,⁵² abaca pulp⁵³ *etc.* Cellulose can also be extracted from waste paper⁵⁴ and textile waste fabrics.⁵⁵

Chitin, chitosan, and cellulose are natural biopolymers widely studied for their structural and functional properties. These materials share several characteristics, including their polysaccharide nature, biodegradability, and applications in biotechnology.⁵⁶ Despite structural differences, these biopolymers exhibit hydrophilic properties, influencing their solubility and applications. Chitosan, unlike chitin and cellulose, is soluble in acidic solutions, which enhances its usability in biomedicine and environmental science.⁵⁷ Chitosan is widely applied in wastewater treatment, removing heavy metals and contaminants, while cellulose derivatives contribute to sustainable agriculture.^{58,59} Additionally, all three materials are also used in wound healing and drug delivery due to their ability to form films and absorb impurities.⁶⁰ Their biodegradability and film-forming ability enable environmentally friendly packaging and bioplastics production.⁶¹ In the food industry, chitosan-based coatings improve food preservation, while cellulose enhances dietary fiber content.⁶² In cosmetics, chitosan aids skin hydration and hair care, whereas cellulose-based polymers serve as anti-aging agents.^{63,64}

While several reviews have extensively discussed the chemistry, modifications, and applications of cellulose, chitin, and chitosan, limited comprehensive analysis focuses specifically on their extraction from diverse natural and industrial waste sources. This

review fills that gap by providing a comparative overview of biological and chemical extraction techniques applied to various waste materials, with detailed tabular data on extraction parameters, sustainability concerns, and source-specific challenges.

2. Manuscript collection and search strategy

A comprehensive and methodical literature search was conducted to support the development of a focused and evidence-based review on the extraction of cellulose, chitin, and chitosan from both natural and waste-derived sources. The aim was to identify high-quality, peer-reviewed studies that contribute meaningfully to environmental sustainability and waste valorization. Special attention was given to publications that described chemical and biological extraction techniques and assessed their efficiency, scalability, and ecological impact.

To ensure rigor and transparency, well-defined inclusion and exclusion criteria were applied, including the relevance to the review topic and publication within the last 10 to 15 years. A multi-stage screening process was employed, and the search encompassed several major scientific databases. The complete methodology, including search parameters, keyword strategies, filters applied, and selection criteria, is summarized in Table 1.

3. Chitin and chitosan

Chitin has two forms. The deacetylated form of chitin is known as chitosan. Chitin and chitosan are composed of two polymers collectively known as glycosaminoglycans. Glycosaminoglycans are a group of glucosamine and acetylglucosamine. A polymer composed only of acetylglucosamine is called chitin, and one composed only of glucosamine is called chitosan. Chitin can be converted into chitosan. As chitin is composed of an unbranched *N*-acetyl-*D*-glucosamine chain, and chitosan consists of only *D*-glucosamine. The *N*-acetyl part is absent in chitosan. Therefore, if the acetyl groups are removed from chitin, it converts into chitosan. That is how chitosan is produced.⁶⁵ We can define chitin and chitosan based on solubility. Based on the property, whether it is soluble or not in 0.1 M acetic acid, chitin and chitosan should be categorized using the terminology suggested by the European Chitin Society (EUCHIS); chitosan is the name for the soluble substance, while chitin is the term for the insoluble one.⁶⁶

3.1 Chemical structure

3.1.1 Chitin. While researching the cuticle of some insects, Antoine Odier discovered it in 1823. He named it chitin, derived from the Greek word “chiton”, which means cloak or wrap. Children discovered nitrogen in 1824 by removing chitin from the elytra of May bugs. In 1843, nitrogen was also observed by Payen, Fischer, and Leuchs. Its primary component, according to Karrer and Zechmeister, is *N*-acetylglucosamine. Early in the 20th century, Meyer and Pankow used X-ray diffraction experiments to validate the structure of chitin.⁶⁷ Chitin is one of the most easily available natural polymers.^{67–69} The structure of



Table 1 Literature search methodology

Step	Description
Databases used	ScienceDirect, Royal Society of Chemistry, Scopus, PubMed, SpringerLink, ACS, and Google Scholar
Search keywords	Chitin extraction from waste, chitin and chitosan extraction method, chitosan extraction biological method, green extraction of chitosan Cellulose from cotton waste, chemical vs. biological extraction of chitin/chitosan, cellulose from newspaper, cellulose extraction from agricultural waste, cellulose from plant source, cellulose extraction method
Time Frame	Publications from 2010 to 2024
Language	English only
Inclusion criteria	<ul style="list-style-type: none"> • Peer-reviewed journal articles • Experimental and review papers with detailed methodology • Studies focused on the extraction of chitin, chitosan, or cellulose from natural or waste sources • Studies describing detailed extraction methodologies (chemical, biological, or combined) • Research involving green, eco-friendly, or sustainable extraction techniques • Papers that include quantitative data (<i>e.g.</i>, yield, purity, deacetylation degree, crystallinity index, <i>etc.</i>) • Articles discussing novel or advanced technologies (<i>e.g.</i>, enzymatic, microbial, or nano-based extraction methods)
Exclusion criteria	<ul style="list-style-type: none"> • Review papers that consolidate extraction processes, challenges, and sustainability considerations • Non-English papers • Duplicate entries • Articles without relevant extraction data • Non-peer-reviewed sources (<i>e.g.</i>, blog posts, conference abstracts, patents) • Focused only on applications
Screening process	<ul style="list-style-type: none"> • Titles, abstracts, and conclusions were screened first • Full texts were reviewed for relevance and quality
Number of studies reviewed	Approx. 200 articles were reviewed and evaluated

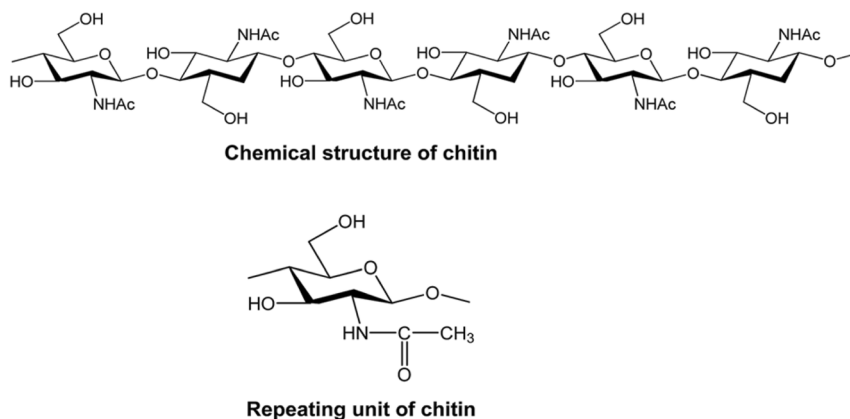
chitin and cellulose is quite similar. The only difference is that, unlike cellulose at carbon number 2, chitin has the *N*-acetyl group (in Fig. 1), whereas cellulose has a hydroxyl group there.⁷⁰

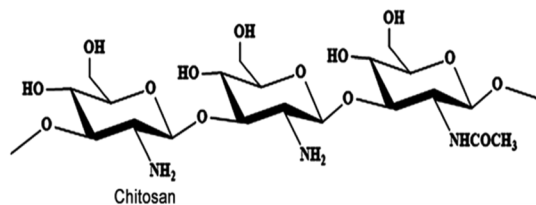
Chitin comes in three different forms: α , β , and γ . The α -form is abundantly available and mostly found in crab and shrimp shells. Commercially, α and β chitin/chitosan are both accessible. The alignment of the α -chitin chains is antiparallel, accompanied by strong hydrogen bonds, which increases their stability. The γ -form of chitin has two parallel and one antiparallel strand, while the β -form, which is primarily found in mollusks like squid, is oriented in parallel. When γ -chitin is treated with lithium thiocyanate, the reagent interacts with the chitin chains, breaking weaker hydrogen bonds and facilitating the rearrangement of the molecular structure. This process

leads to the transformation of γ -chitin into the more stable α -chitin form.⁷²

3.1.2 Chitosan. Chitosan is a polymer made entirely of glucosamine. It is a naturally occurring biopolymer derived from chitin, the primary structural element of squid pens, shrimp and crab shells, and the cell walls of some fungi.⁷² Rouget discovered that heating chitin in an alkaline medium produced a substance soluble in organic acids in 1859. Hoppe-Seyler named this substance chitosan in 1894, but its chemical makeup was not determined until 1950.⁷⁰ High temperature and strong alkali treatment are required for the deacetylation process of chitin to convert it into chitosan (Fig. 2).⁷³

The deacetylation process results in converting the acetamide groups of chitins into primary amino groups. This

Fig. 1 Chemical structure of chitin.⁷¹

Fig. 2 Chemical structure of chitosan.⁷⁴

polysaccharide is natural, biocompatible, recyclable, non-toxic, and antibacterial. It comes in various forms, including solution, powder form, flake, fiber, and film.⁷⁵

3.2 Elemental composition of chitin and chitosan polymer

Name	Carbon %	Nitrogen %	Hydrogen %	Ref.
Chitin	47.3	6.5	6.9	76
Chitosan	44.11	7.97	6.84	72

4. Extraction process of chitin and chitosan

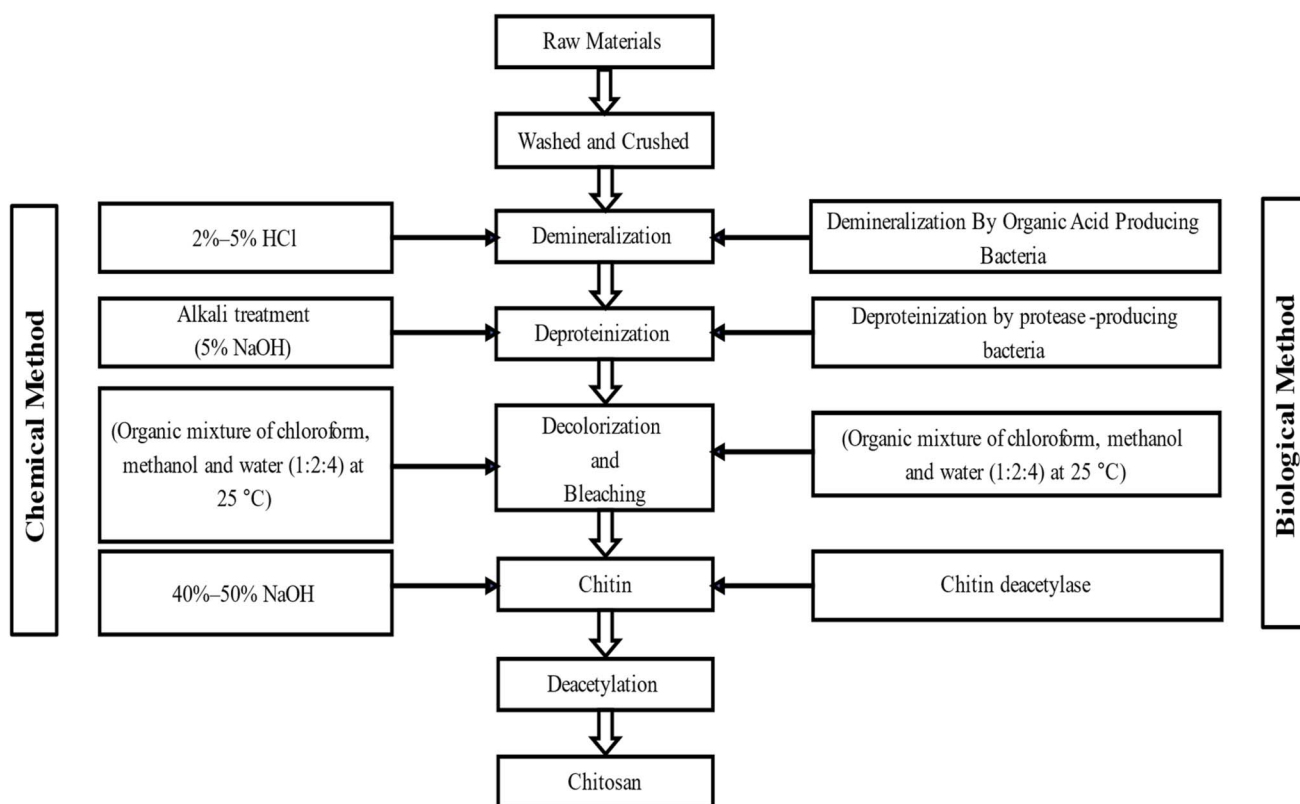
Chitin and Chitosan are extracted mainly from crab shells and sea shrimp crustaceans. This extraction is done using (1) Chemical method and (2) Biological method.⁷⁷

4.1 Chemical method

Deproteinization, demineralization, and discoloration are the three main steps of the chemical extraction method. Among all extraction methods, the chemical extraction method is mostly used. Deproteinization is mainly the depolymerization of biopolymers, which breaks down the bond between the chitin and protein. Demineralization is done using strong acids like H₂SO₄, HCl, HCOOH, HNO₃, and CH₃COOH to remove calcium carbonate and other minerals (Fig. 3).⁷⁷ Generally, calcium carbonate reacts with acids and produces salt, water molecules, and carbon dioxide (in eqn (1)).⁷⁸ Then the discoloration process is done to get a colorless product by removing pigments like β-carotene and astaxanthin. Mainly, acetone is used in this process.⁸



Suneeta Kumari *et al.* used three natural waste sources to extract chitin. They used *Labeo rohita* as fishery waste, the shell of *Crangon crangon* as Crab waste for the source of chitin.⁷⁹ At first, they removed the protein matter from their sources (3% NaOH, 30 min, 80 °C), removed minerals, and extracted chitin by treating them with 3% HCl for 30 minutes at room temperature. Then they deacetylated chitin to produce chitosan (40% KOH, 6 hours, 90 °C). The degree of deacetylation of chitosan obtained from fish, shrimp, and crab was 75%, 78%, and 70%, respectively.⁷⁹

Fig. 3 Flow sheet of the extraction process of chitin and chitosan.^{8,79}

Microwave irradiation can be incorporated with the chemical extraction process to improve the quality and reduce the time required for the chemical reactions. El Knidri H. and El Khalfaouy combined microwave heating with the conventional chemical extraction process. The deacetylation process took around 24 minutes with microwave heating, whereas the traditional method needed 6.5 hours. The degree of deacetylation with microwave irradiation was slightly higher than that of the chitosan obtained by the traditional heating method (82.73% and 81.50%, respectively). Moreover, the molecular weight of the microwave-heated chitosan was higher.⁸⁰

4.2 Biological methods

Besides chemical methods, biological methods are also available to prepare chitosan. There are two types of biological methods: (1) Enzymatic method (2) Fermentation method.⁷⁰

This method is more environmentally friendly as it requires no harsh chemicals. Acid-producing bacteria and protease-producing bacteria are mainly used in this process for demineralization and deacetylation. This process is time-consuming compared to other processes. The efficiency and quality are low as well. That is why this is a costly process with less industrial usage.⁸¹

4.2.1 Enzymatic method. There is no difference between chemical and enzymatic methods for the demineralization process. The biological extraction process involves enzymes and microorganisms to extract chitin from its sources. The enzyme protease does the deproteinization process (Fig. 3). Pepsin, trypsin, papain, alkaline, pancreatin, *etc.*, are some commonly used proteases. The primary sources of these proteases are plants, microorganisms, and animals. Based on some parameters, biological extraction is better than the chemical extraction process because it is more environmentally friendly and does not change the structure of chitin.⁸

In this method, acid removes the CaCO₃ in the shell.^{70,82} As this method uses proteinases for enzymatic deproteinization and deacetylases extracted from microbes and fish intestines for deacetylation, the application of elevated temperatures and strong alkali treatment is eliminated. This makes the method more environmentally friendly.^{83,84} For example, Alcalase is obtained from *Bacillus licheniformis*. This method follows complex reaction mechanisms. Using an acid/base reaction mechanism, CE4 (a member of the carbohydrate esterase enzyme family) may remove *N*-acetyl functional groups when metal ions (often zinc or cobalt) are attached to the enzyme's reaction site.⁸⁵

Furthermore, this method's degree of deacetylation value is much lower, and this method is less effective than chemical methods because the enzymatic method cannot remove the last 10% of the proteins during deproteinization.⁸⁶ Fermentation techniques have been created as an option for solving the problem of the high cost of enzymes. This is because microorganisms may multiply while secreting enzymes into reactors under optimal reaction conditions, hence lowering the cost of enzymes.^{86,87}

4.2.2 Fermentation method. The fermentation process is used in place of the enzymatic method for making chitin or chitosan. Various types of bacteria are used for this fermentation process. Bacteria that produce lactic acid are used in the lactic acid fermentation process. Also, bacteria that produce other organic acids rather than lactic acid are used in non-lactic acid fermentation. These lactic or other types of organic acids produced by the bacteria cause the demineralization of raw materials (Fig. 3). When calcium carbonate and lactic acid combine, calcium lactate is produced, which may be precipitated and eliminated.⁷⁰ Moreover, the deacetylation process to convert chitin into chitosan can be carried out by acetyl xylan esterase.⁶⁶

Aranday-García used *Lactobacillus brevis* (20% v/w) and *Rhizopus oligosporus* for the demineralization and deproteinization, respectively.⁸⁸ They inoculated shrimp shells with *Lactobacillus brevis* and sucrose (10% w/w) for 2 hours at 30 °C. Following that, they added *Rhizopus oligosporus* and glucose (10% w/w) and incubated for 72 hours. The culture was then kept for fermentation for 8 days. After 8 days of fermentation, the chitin was rinsed with water and dried. The remaining mineral and protein content was removed by the conventional method (HCl 0.4 N 25 °C for 2 hours and NaOH 0.5 N 25 °C for 2 hours). The final product was obtained by rinsing the sample with distilled water and drying it for 2 days at 40 °C. The efficiency of deproteinization and deacetylation was 96.8% and 97.5%, respectively.⁸

4.3 Combined chemical and biological methods

A combination of chemical and biological processes can extract chitin and chitosan. Younes and Hajji used enzymatic protease for deproteinization and conventional acid alkali methods for demineralization and deacetylation because chitin produced by deproteinization by enzymatic proteases has higher molecular weights compared to chitin which is obtained by chemical deproteinization.⁸² Several microbial and fish alkaline proteases were used for the deproteinization of shrimp shells. They digested shrimp shells with enzymes for 3 hours and stopped the reaction by heating the solution for 20 minutes at 90 °C to inactivate the enzymatic action. The solid product obtained from the enzymatic action of *Bacillus mojavensis* A21 and *Balistes capriscus* proteases was treated with HCl (1.5 M, 25 °C, 6 hours) for demineralization. After that, they were treated with NaOH (12.5 M, 12 hours, 50 °C) for deacetylation. The efficiency of deproteinization by *Bacillus mojavensis* A21 and *Balistes capriscus* was 77 ± 3% and 78 ± 2%, respectively.⁸²

4.4 Sources of chitin and chitosan

The extraction processes described in Sections 4.1 to 4.3 serve as the basis for evaluating how chitin and chitosan can be obtained from different biological sources. This section explores how these methods are applied to various organisms, emphasizing waste.

There are several sources from which chitin may be extracted. Chitin is commercially extracted from the shells of shrimp, crabs, crab fish, and krill. According to some recent research,



other sources of chitin include insects, mushrooms, coral, and resting eggs from crustaceans.⁷⁹

4.4.1 Shrimp sources. The contents of shrimp biowaste and fish scales are 15–30% chitin, 30–65% protein, 30–50% minerals, and 10–20% calcium, respectively.^{79,82} Strong acids and bases can be used to eradicate proteins and calcium carbonate.⁸² The heads, shells, and tails of shrimp comprise 40–50% of their weight worldwide. Environmental problems arise because only 5% of it is used for animal feed, and the remainder is thrown away.^{89,90}

In Table 2, the main chemical is NaOH in the deproteinization step to extract chitin and chitosan from shrimp sources, whereas HCl is used in the demineralization step. The acetyl group is removed using the strong alkali reagent NaOH in the deacetylation step. During deproteinization, the best conditions for obtaining the maximum chitin yield (36.7–42.1%) and chitosan (64.1–81.9%) were determined to be 10% w/v NaOH at 100 °C for one hour. Raising the NaOH concentration to 48% at room temperature produced a much lower chitosan yield (4.09%), suggesting that milder conditions are better for effective protein removal. To get the maximum yield percentage, 6% (w/v) HCl is used for 2 hours in the demineralization step, and 50% (w/v) NaOH at 60 °C for 4 hours is applied in the deacetylation step. However, the yield percentage of chitosan is the lowest, at 4.09%, when chitin is converted to chitosan using 48% w/v NaOH at room temperature for 48 hours. Chitin and chitosan yield percentage differences are less significant when 50% (w/v) NaOH is employed at 120 °C; they are 30% and 35%, respectively.

The most commonly employed reagents in the chemical extraction of chitin and chitosan are NaOH for deproteinization and deacetylation, and HCl for demineralization. However, using these strong acids and bases raises serious environmental concerns, as they are corrosive, hazardous to handle, and produce toxic effluents. These effluents often require extensive neutralization and treatment before disposal.

4.4.2 Insect sources. Since chitin is mainly sourced from marine waste, the market demand for it now surpasses the supply chain.¹⁰³ The over two million insect species found globally comprise 95% of the animal kingdom. Only a small number of species, such as *Bombyx mori*, *Bombus terrestris*, *Musca domestica*, *Holotrichia parallela*, *Hogna radiata*, and *Geolycosa vultuosa*, have been found to have chitin.¹⁰⁴ The alpha form of insect chitin has physicochemical characteristics similar to crustacea, such as the shells of shrimp and crabs. Chitin from insects is easier to extract and more ecologically friendly since it includes less calcium carbonate (<6%) than that from crustaceans (30–50%). Additionally, it maintains greater degrees of polymerization with enhanced mechanical, gelling, biological, and flexible qualities. Chitin extraction and its conversion into bioproducts or biomaterials from different insect species and body sections have been the subject of several articles during the last five years.¹⁰³

In Table 3, the maximum amount of chitin can be extracted from *Apis mellifera*, and the percentage range is 51 to 77.2%. At this maximum quantity, 1 M HCl and 1 M NaOH are used for demineralization and deproteinization, respectively. However,

the chitin percentage of *Hylobius abietis* is 27.9%, below the maximum amount of chitosan derived from its chitin, which is 86.2%. This source uses 2 M NaOH for 2 hours in the deproteinization stage and 22 M NaOH for 4 hours at 100 °C in the deacetylation phase.

4.4.3 Mushroom sources. Fungi and mushroom wastes are some other sources of chitin and chitosan (Table 4). Unlike chitosan derived from shrimp and crab shells, chitosan extracted from mushroom waste requires less harsh solvents and the process is also simpler. No demineralization process is required to extract chitosan from mushrooms, as mushrooms do not contain any significant amount of metal salts. *Agaricus bisporus* is the most consumed mushroom in the USA, and it is also a good source of chitinous biopolymer. Wu, T. and Zivanovic S. extracted chitosan from stalks of White button mushrooms, *A. bisporus*. To remove proteins, alkali-soluble polysaccharides, and other small molecules, the stalks were stirred in NaOH (1 M, 30 minutes, 95 °C). The remaining insoluble part was then separated by centrifugation and washing and treated with 2% acetic acid (95 °C, 6 hours) to extract acid-insoluble chitin. Chitin was then converted into chitosan by the treating acetic acid at a pH of 10. Their yield was up to 27% and the degree of deacetylation was from 75.8 to 87.6%.^{115,135}

Chitosan might be produced using the chitin fibers found in the cell walls of mushrooms. Different mushrooms have been reported to produce chitosan. However, quality mushrooms may not be required, and waste from the mushroom business might be useful.¹³⁶ Fungal cell walls are complex structures composed of polysaccharides, including chitin/chitosan. The exterior layers of most fungi are more varied and adapted to the physiology of a particular fungus, whereas the inner wall layer is composed of branching β -(1,3) glucan, β -(1,6) glucan, and chitin and is alkali-insoluble.¹³⁷ With few members in the Ascomycotina division, mushrooms belong to the higher fungus division, basidiomycetes. With mycelia networks of hyphae, they are recognizable and fleshy. Being saprophytes, mushrooms may grow in a variety of habitats and substrates. Because of their excellent flavor and high protein content, they have been regarded as an important meal for millennia. A few types of mushrooms have also been used medicinally. Tree trunk tissues, fallen logs, or other nutrient-rich substrates can all support the growth of mushrooms.¹³⁸

In the deproteinization stage, chitin and chitosan are extracted from mushroom specimens using NaOH, acetic acid, oxalic acid, C₂H₅OH, HCl, and Na₂S₂O₅. Alkaline solutions (NaOH, NH₄OH) and acidic solutions (CH₃COOH, HCl) are used to convert chitin into chitosan during the deacetylation step. Temperature and time vary from chemical to chemical.

4.4.4 Annelida sources. There are various kinds of annelida sources from which chitin and chitosan are extracted, including *Egeria radiata*,¹⁴⁸ *Ensis arcuatus*,¹⁴⁹ *Pinna deltoidea*,¹⁵⁰ *Mytilus edulis*,¹⁵¹ Oyster shell,¹⁵² Chiton shell,¹⁵³ *Acanthopleura vaillanti*,¹⁵⁴ Mussel shell,¹⁰² *Halotis tuberculata*,¹⁵⁵ *Modiolus modiolus*,¹⁵⁰ *Bellamya jayanica*,¹⁵⁶ *Donax scrotum*,¹⁵⁷ *Murex trapa*,¹⁵⁸ *Anadara granosa*,¹⁵⁹ *Conus inscriptus*,¹⁶⁰ Snail shells,¹⁶¹ *Perna viridis*¹⁶² etc. Generally, in demineralization and





Table 2 Extraction methods, conditions, and sources of chitin and chitosan from shrimp shell waste

Deproteinization				Deminerzalization				Deacetylation				Yield		References
Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration	Temp. (°C)	Chitin %	Chitosan %	
NaOH	15% (w/v)	3 h	65	HCl	1 N	2 h	—	NaOH	65% (w/v)	1 h	100	—	—	91
NaOH	10% (w/v)	2 h	80	HCl	3 M	2 h	75	NaOH	50% (w/v)	2.5 h	100	—	—	80
NaOH	3% (w/v)	30 min	80	HCl	3% (w/v)	30 min	25	KOH	40% (w/v)	6 h	90	—	—	79
NaOH	2.5 M	20 min	121	HCl	1.5 M	6 h	25	NaOH	12.5 M	4 h	140	—	—	82
NaOH	2 N	2 h	50	HCl	2 N	2 h	25	NaOH	50% (w/v)	1 h	121	14.72 ± 0.57	12.03 ± 0.46	92
NaOH	1 M	24 h	—	HCl	1 M	—	—	NaOH	50% (w/v)	—	—	—	—	93
NaOH	0.5% (w/v)	30 min	100	HCl	1.5 N	1 h	25	NaOH	42% (w/v)	1.5 h	95	—	—	94
NaOH	4% (w/v)	21 h	25	HCl	4% (w/v)	12 h	25	NaOH	50% (w/v)	3 days	40	—	—	94
NaOH	3 M	75 min	25	HCl	1 M	75 min	25	NaOH	50% (w/v)	1.5 h	90	30	35	89
NaOH	2.5 N	6 h	65	HCl	1.7 N	6 h	25	NaOH	50% (w/v)	—	120	—	17.5	95
NaOH	2 and 4% (w/v)	1 h	100	HCl	1% (w/v)	24 h	—	NaOH	50% (w/v)	2 h	100	—	34	96
NaOH	1 M	—	105–110	HCl	1 M	—	25	NaOH	—	>20 h	—	21.53 brown shrimp	—	97
NaOH	10% (w/v)	1 h	100	HCl	6% (w/v)	2 h	—	NaOH	50% (w/v)	4 h	60	—	—	98
NaOH	2 N	4 h	70	HCl	3.25 N	4 h	25	NaOH	8.75 N	75 h	25	36.7 to 42.1	64.1 to 81.9	74
	1.25 N	24 h	90	HCl	1.3 N	24 h	25		17.5 N	75 h	25	—	—	
	1.25 N	3 h	70	HCl	0.32 N	24 h	25°		12.5 N	12 h	100	—	—	
	1 M	24 h	25	HCl	1 N	24 h	25		50% (w/v)	24 h	25	—	—	
				NaOH	1 N	24 h	25					—	—	
NaOH	1 M	—	70	HCl	1 M, 0.25 M	24 h	25	NaOH	45% (w/v)	—	110	19.13	—	99
NaOH	2 M	48 h	25	HCl	1 M	—	25	NaOH	48% (w/v)	48 h	25	—	4.09	99
NaOH	0.5 M	18 h	25	HCl	1 M	12 h	—	NaOH	—	5–6 h	—	—	—	100
NaOH	4% (w/v)	24 h	25	HCl	4% (w/v)	24 h	25	NaOH	65% (w/v)	3 days	25	—	46	8
NaOH	5% (w/v)	2 h	60	HCl	0.5–1% (w/v)	6 h	25	NaOH	25% (w/v)	2 h	80	—	—	101
									50% (w/v)	5 h	100	—	—	
NaOH	0.68 M	16 h	30	HCl	0.68 M	—	30	NaOH	25 M	20 h	75	—	—	102



Table 3 Chitin and chitosan from insect biomass: species, pretreatment approaches, and process parameters

Insect species	Deproteinization			Deminereralization			Deacetylation			Yield		References			
	Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration		Temp. (°C)	Chitin %	Chitosan %
<i>Gryllus bimaculatus</i>	NaOH	1 M	3 h	95	—	—	—	—	NaOH	19–25 M	15 h	—	5.1	41.7 (from chitin)	105
<i>Dociostaurus maroccanus</i>	NaOH	2 M	18 h	50	HCl	2 M	1 h	55	NaOH	22 M	4 h	150	12–14	81.7 (from chitin)	106
<i>Acheta domestica</i>	NaOH	1 M	—	95	C ₂ H ₂ O ₄	0.1 M	3 h	25	—	—	—	—	4.3–7.1 (from biomass)	2.3–5.8 (from biomass)	107
<i>Apis mellifera</i>	NaOH	1 M	6–64 h	80	HCl	1 M	1 h	25	—	—	—	—	51–77.2	—	108
<i>Hermetia illucens</i>	NaOH	2 M	2 h	80	CH ₂ O ₂	0.5 M	1 h	25	NaOH	12 M	6-Mar	120–140	31–35	8–16 (from biomass)	109
<i>Agabus bipustulatus</i>	NaOH	1 M	18 h	110	HCl	1 M	1 h	90	NaOH	22 M	2 h	120	14–15	71 (from chitin)	110
<i>Anax imperator</i>	NaOH	—	—	—	—	—	—	—	—	—	—	—	11–12	67 (from chitin)	70
<i>Ranatra linearis</i>	NaOH	—	—	—	—	—	—	—	—	—	—	—	15–16	70 (from chitin)	69
<i>Notonecta glauca</i>	NaOH	—	—	—	—	—	—	—	—	—	—	—	10–11	69 (from chitin)	111
<i>Celes variabilis</i>	NaOH	4 M	20 h	150	HCl	4 M	2 h	75	—	—	—	—	6.6–9.9	—	111
<i>Melanogryllus desertus</i>	NaOH	4 M	20 h	150	HCl	4 M	2 h	75	—	—	—	—	4.7–7.3	—	111
<i>Decticus verrucivorus</i>	NaOH	2 M	16 h	80–90	HCl	2 M	2 h	65–75	NaOH	19 M	3 h	100	Jul-20	72 (from chitin)	104
<i>Leptinotarsa decemlineata</i>	NaOH	1 M	24 h	80	HCl	1 M	0.6 h	80	—	—	—	—	3.3	—	103
<i>Bombyx eri</i>	NaOH	1 M	18 h	150	HCl	4 M	—	75	—	—	—	—	—	—	112
<i>Melolontha melolontha</i>	NaOH	4 M	18 h	150	HCl	2 M	2 h	75	—	—	—	—	—	—	113
<i>Vespula germanica</i>	NaOH	2 M	24 h	50	HCl	2 M	24 h	50	—	—	—	—	—	—	114
<i>Vespa crabro</i>	NaOH	1.9 M	2 h	50	HCl	0.5 M	2 h	25	NaOH	19 M	2 h	100	46	80 (from chitin)	115
<i>Argynnis pandora</i>	NaOH	2 M	2 h	—	HCl	2 M	—	25	NaOH	22 M	4 h	100	27.9	86.2 (from chitin)	116
<i>Hermetia illucens</i>	NaOH	3 M	20 h	70	HCl	2 M	3 h	40	NaOH	22 M	48 h	150	7.8	71 (from chitin)	117
<i>Hylobius abietis</i>	NaOH	1 M	21 h	80–90	HCl	1 M	30 min	100	NaOH	19 M	2 h	130	20.5	74 (from chitin)	118
<i>Drosophila melanogaster</i>	NaOH	2 M	20 h	100	HCl	2 M	20 h	60	—	—	—	—	16.5	75 (from chitin)	119
<i>Calliptamus barbarus</i>	NaOH	2 M	20 h	100	HCl	2 M	20 h	60	—	—	—	—	—	—	—
<i>Oedaleus decorus</i>	NaOH	2 M	20 h	100	HCl	2 M	20 h	60	—	—	—	—	—	—	—
<i>Melolontha sp.</i>	NaOH	2 M	20 h	100	HCl	2 M	20 h	60	—	—	—	—	—	—	—



Table 3 (Contd.)

Insect species	Deproteinization				Demineralization				Deacetylation				Yield		References
	Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration	Temp. (°C)	Reagent	Strength	Duration	Temp. (°C)	Chitin %	Chitosan %	
<i>Musca domestica</i>	NaOH	1.25 M	3 h	95	HCl	2 M	3 h	25	NaOH	19 M	05-Mar	95–105	7.7–8.5	6.8	120
<i>Cicada</i>	NaOH	1 M	—	80	HCl	1 M	2 h	30	NaOH	22 M	8 h	100	—	28.2	81
<i>Bombyx mori</i>														3.1	
<i>Grasshopper</i>														5.7	
<i>Tenebrio molitor</i>														2.5	
<i>Gryllus bimaculatus</i>	NaOH	1.25 M	3 h	95	HCl	2 M	3 h	25	NaOH	19 M	3 h	100	2.4	1.8	81
<i>Catharsius molossus</i>	NaOH	4 M	6 h + 12 h	90 + 25	HCl	1.3 M	30 min + 12 h	80 + 25	NaOH	18 M	24 h + 7 h	25–95	24	—	121
<i>Calosoma rugosa</i>	NaOH	1 M	8 h	100	HCl	1 M	25	—	NaOH	19 M	8 h	100	5	—	122
<i>Apis mellifera</i>	NaOH	1 M	24 h	82	HCl	1 M	30 min	97	NaOH	15 M	—	105–110	10.4	8.1	123
<i>Brachystola magna</i>															
<i>Bombyx mori</i>	NaOH	1 M	3 h	80	HCl	1 M	—	100	NaBH ₄	0.25 g L ⁻¹	—	—	15–20	—	124
<i>Beetle</i>															
<i>Musca domestica</i>	NaOH	1 M	3 h	100	—	—	—	—	NaOH	15 M	4 h	110	—	60–70	125
														(from chitin)	
<i>Apis mellifera</i>	NaOH	15 M	—	—	—	—	—	—	NaOH	19 M	1 h	150	—	—	126
<i>Cryptotympana atrata</i>	NaOH	3.7 M	24 h	60	HCl	2 M	24 h	25	NaOH	21 M	4 h	110	—	—	127
<i>Calliphora erythrocephala</i>	NaOH	1 M	2 h	50	—	—	—	—	NaOH	19 M	1–4 h	100–120	12.2	66.7	128
<i>Clanis bitineata</i>	NaOH	3.7 M	24 h	60	HCl	2 M	24 h	25	NaOH	21 M	4 h	110	—	(from chitin)	127
<i>Bombyx mori</i>	NaOH	1 M	—	80	HCl	1 M	—	100	NaOH	15 M	—	100	2.6–4.3	—	129
<i>Hermetia illucens</i>	NaOH	1 M	24 h	80	HCl	1 M	—	—	NaBH ₄	1 g L ⁻¹	—	—	—	—	130
<i>Allomyrina dichotoma</i>	NaOH	3.7 M	24 h	80	HCl	2 M	24 h	25	NaOH	21 M	9 h	90	—	83.4	131
<i>Mayfly</i>	NaOH	2 M	—	100	HCl	2 M	—	50	NaOH	22 M	6 h	150	10.2	78.4	132
														(from chitin)	
<i>Chrysomya megacephala</i>	NaOH	1 M	6	95	C ₂ H ₂ O ₄	0.1 M	3	—	NaOH	25 M	9 h	90	—	26.2	133
<i>Zophobas morio</i>	NaOH	0.5–2 M	20	80	HCl	1 M	30 min	35	NaOH	19 M	30 h	90	—	65–75	134
														(from chitin)	



Table 4 Chitin and chitosan recovery from mushroom-based fungal sources: extraction processes and parameters

Mushroom specimen	Deproteinization				Deacetylation				Yield %		References	
	Reagent	Strength	Duration	Temp. (°C)	Reagents	Strength	Duration	Temp. (°C)	pH	Chitin		Chitosan
White <i>A. bisporus</i> , brown <i>A. bisporus</i> , <i>P. ostreatus</i>	Ethanol	96% (v/v)	15 min	—	NaOH	50% (v/v)	2 h	104	8.5	—	—	139
	Na ₂ S ₂ O ₅ + HCl	0.5% (m/v)	1 h	25	HCl	1 M	—	—	—	—	—	—
	NaOH	2%	2 h	56	—	—	—	—	—	—	—	—
White <i>A. bisporus</i>	NaOH + H ₂ O ₂	0.1 M + 3% (v/v)	30 min	45	—	—	—	—	—	—	—	140
	NaOH	1 M	2 h	80	NH ₄ OH	37% (v/v)	—	—	9	7.4	—	—
	Acetic acid	2% (v/v)	6 h	95	NaOH	2 M	—	—	10	—	—	136
White <i>A. bisporus</i>	NaOH	2 M	2 h	100	—	—	—	—	—	—	—	—
	Oxalic acid	1% (w/v)	1 h	100	—	—	—	—	—	—	—	—
	Acetic acid	2% (v/v)	2	90	—	—	—	—	—	—	—	—
<i>Pleurotus ostreatus</i>	NaOH	1 M	3 h	90	NaOH	10 M	3 h	90	9	—	—	137
<i>A. bisporus</i> , <i>Pleurotus</i> , <i>Ostreatus</i> , <i>Ganoderma</i> <i>lucidum</i>	NaOH	1–4 M	15 min	95, 110, 121	NaOH	—	24 h	4	—	—	19.7	141
	Acetic acid, HCl	2%, 6%, 10%	3 h, 6 h, 12 h	60, 95	—	—	—	—	—	—	41.29	—
	NaOH	1 M	30 min	95	—	—	—	—	10	—	—	135
<i>A. bisporus</i>	Acetic acid	2% (w/v)	6 h	95	—	—	—	—	—	13.98	—	—
	NaOH	1 M	15 min	121	NaOH	2 M	—	—	09-Oct	—	—	142
	Acetic acid	0.35 M	5 h	95	—	—	—	—	—	—	—	143
<i>A. bisporus</i>	NaOH	1 M	2 h	80	—	—	—	—	—	—	—	—
	Acetic acid	2% (v/v)	6 h	95	NaOH	2 N	—	—	12	—	—	138
	NaOH	1 N	3 h	100	—	—	—	—	—	—	—	—
<i>Pleurotus ostreatus</i>	Acetic acid	2%	5 h	100	—	—	—	—	—	—	—	—
	NaOH	1 N	12 h	40	NaOH	47%	2 h	60	—	—	—	144
	Acetic acid	5%	3 h	90	—	—	—	—	—	8.5 ± 1.4	—	145
<i>Pleurotus ostreatus</i> , <i>Schizophyllum commune</i>	NaOH	1 M	24 h	25	NaOH	40%	—	—	—	—	1.22	145
	NaOH	1 M	2 h	45	NaOH	1 N, 2 N	20 min	121	—	—	1.73	146
	NaOH	1 M	2 h	40	Acetic Acid	2% (v/v)	5 h	95	—	—	—	147
<i>Ganoderma lucidum</i> <i>Ganoderma lucidum</i>	NaOH	1 M	2 h	100	—	—	—	—	—	41	—	—
	NaOH	4 M	2 h	100	NaOH	45%	2 h	60	—	—	—	—



Table 5 Extraction of chitin and chitosan from annelid sources: treatment steps and processing conditions

Source	Demimeralization				Deproteinization				Deacetylation				Yield (%)		
	Reagent	Strength	Duration	Duration	Reagent	Strength	Duration	Temp. (°C)	Reagents	Strength	Duration	Temp. (°C)	Chitin	Chitosan	Reference
<i>Egeria radiata</i>	HCl	4% w/v	12 h	12 h	NaOH	65% w/m	3 days	25	NaOH	4% w/v	24 h	25	—	48.6	148
<i>Ensis arcuatus</i>	HCl	20%	16.5 h	16.5 h	NaOH	50%	10 h	90	NaOH	10%	2 h	70	—	19.36	149
<i>Ensis arcuatus</i>	HCl	1 M	2 h	2 h	NaOH	—	—	—	—	1 M	5 h	40	—	—	164
<i>Pinna deltoidea</i>	HCl	1 M	15 min	15 min	NaOH	45%	24 h	110	NaOH	1 M	20 min	100	70.67	45.01	150
<i>Mytilus edulis</i>	HCl	4% v/v	12 h	12 h	NaOH	65% w/v	3 days	25	NaOH	4% w/v	24 h	25	—	51.8	151
<i>Laevicardium attenuatum</i>															
Oyster shell	HCl	1 N	2 h	2 h	NaOH	50%	1 h	120	NaOH	3 N	2 days	90	30.01	61.1	152
Chiton shell	HCl	1 M	3 h	3 h	NaOH	5%	5, 15, 24 h	110	NaOH	1 M	3 days	70	4.3	—	153
Oyster shell	HCl	10%	3 days	3 days	NaOH	—	—	—	—	10%	24 h	30	69.65	—	154
<i>Acanthopleura vaillantii</i>	HCl	1 M	3 h	3 h	NaOH	5%	24 h	110	NaOH	1 M	—	70	—	—	153
Mussel shell	HCl	0.68 M	6 h	6 h	NaOH	25 M	20 h	75	NaOH	0.62 M	16 h	30	23.25	15.14	102
<i>Haliois tuberculata</i>	25	—	HCl	HCl	30 min	NaOH	1 M	8 h	—	—	—	—	—	0.064	155
<i>Modiolus modiolus</i>	70	100	HCl	HCl	15 min	NaOH	1 M	20 min	110	NaOH	45%	24 h	40.13	10.21	150
<i>Bellamyia javanica</i>	—	—	HCl	HCl	30 min	NaOH	4%	2 h	120	NaOH	60%	1 h	21.76	—	156
<i>Donax scortum</i>	—	80	HCl	HCl	24 h	NaOH	1 N	24 h	110	NaOH	40%	6 h	11.96	18.8	157
<i>Murex trapa</i>	25	70	HCl	HCl	2 days	NaOH	5%	2 days	90	NaOH	40%	6 h	—	17	158
<i>Anadara granosa</i>	—	—	HCl	HCl	2 days	NaOH	3.5 N	1 h	80	NaOH	50%	3 h	—	—	159
<i>Conus inscriptus</i>	60	80	HCl	HCl	30 min	NaOH	3 M	2 h	100	NaOH	50%	2 h	21.65	—	160
<i>Anadara granosa</i>	75	85	HCl	HCl	1 h	NaOH	3%	30 min	—	NaOH	45%	1 h	—	—	163
Snail shells	25	60	HCl	HCl	6 h	KOH	2%	24 h	105	NaOH	40%	2 h	—	—	161
<i>Perna viridis</i>	—	—	HCl	HCl	—	NaOH	1 N	—	—	25	15%	24 h	41.6	39.5	162
<i>Monacha cantiana</i>	—	—	HCl	HCl	24 h	NaOH	2–4%	1 h	100	NaOH	50%	2 h	—	—	165
<i>Crassostrea iredalei</i>	75	80	HCl	HCl	2 h	NaOH	1 M	2 h	100	NaOH	50%	2 h	22.5	11.8	166
<i>Pomacea canaliculata</i>	25	65–100	HCl	HCl	2–3 h	NaOH	1–10%	2 days	100	NaOH	40–50%	—	—	17.48	167
<i>P. viridis</i>	25	70	HCl	HCl	2 days	NaOH	5%	2 days	90	NaOH	40%	6 h	—	18	168
<i>Telescopium telescopium</i>	25	70	HCl	HCl	2 days	NaOH	3%	2 days	—	NaOH	60%	4 h	42	—	169
<i>P. viridis</i>	25	70	HCl	HCl	2 days	NaOH	3%	2 days	—	NaOH	60%	3.5 days	—	—	170
<i>Doryteuthis singhalensis</i>	90	60	HCl	HCl	2 h	NaOH	—	3 h	90	NaOH	40%	2 h	37.65	85	171
<i>Amusium</i> sp.	90	90	HCl	HCl	2 h	NaOH	5%	140 min	90	NaOH	50%	—	—	9.7	172
<i>Doryteuthis sibogae</i>	—	80	HCl	HCl	24 h	NaOH	1 N	24 h	110	NaOH	40%	6 h	33.02	—	173
<i>S. kobensis</i>	90	60	HCl	HCl	2 h	NaOH	—	3 h	90	NaOH	40%	2 h	29.87	43.77	174
<i>D. gigas</i>	—	25	—	—	—	NaOH	1 M	24 h	—	—	—	—	38.6	—	175
<i>S. officinalis</i>	24	90	HCl	HCl	—	NaOH	4%	20 min	140	NaOH	12.5 M	4 h	5	—	176
Squid pens	—	100	HCl	HCl	2 h	NaOH	10%	1 h	80	NaOH	50%	2 h	—	—	177
Cuttlefish	25	100	HCl	HCl	30 min	NaOH	1 N	1 h	90	NaOH	33%	10 min – 2 h	50	70	70

deproteinization steps, HCl and NaOH are used, respectively, and in the deacetylation step, NaOH is used to convert chitin into chitosan.^{157–160,163}

In Table 5, 70.67% is the highest amount of chitin that can be extracted from *Pinna deltoidea*. Chitin extraction from oyster shells has a 69.65 percent yield, nearly equal to the maximum percentage. The highest chitosan production (85%) is obtained from *Doryteuthis singhalensis*. In the deproteinization stage, protein is removed for two hours at 90 °C using 4 M HCl, and minerals are removed using NaOH in the demineralization stage.

In contrast, 40% NaOH is used in the deacetylation process at 90 °C for two hours. 1 N HCl, 1 N NaOH, and 33% NaOH are the main chemicals used in cuttlefish sources, and the yield is 70%.

5. Cellulose

5.1 Chemical structure of cellulose

Cellulose is a carbon-rich material.⁴⁷ It has axial carbon-hydrogen (C-H) planes that are hydrophobic and hydrophilic

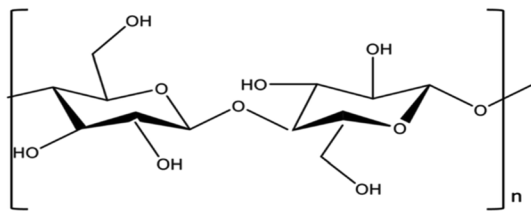


Fig. 4 Chemical structure of cellulose.¹⁸⁰

hydroxyl groups.¹⁷⁸ It is present mainly in plant cell walls. This large-molecule polymer comprises repeated D-glucose units connected by beta-1,4-glycosidic linkages (Fig. 4).¹⁷⁹

There are crystalline and amorphous parts that make up cellulose.⁴⁷ The primary chemical link that is widely distributed is the hydrogen bond, which forms a vast network and directly contributes to the crystalline structure.¹⁷⁹ The amorphous part of cellulose can be hydrolyzed to separate the nanocrystals. Pure cellulose is hydrolyzed using strong acids at a regulated temperature and duration.⁴⁷

5.2 Extraction of cellulose

5.2.1 Extraction of cellulose from waste paper. Waste paper is another good source of cellulose. Old newspapers, recycled newsprint paper, office waste paper, etc., can be used to synthesize cellulose.^{54,181,182} The deinking process on waste paper is done to remove ink and other undesirable contaminants except cellulose.¹⁸³ Papers are shredded into pieces and converted into pulp before mixing the deinking agents in the pulp. This is done by washing or floatation and NaOH, H₂O₂, NaClO, NaClO₂, surfactant sodium dodecyl benzene sulfonate (SDBS), and NaSiO₃ etc. are some common deinking agents (Table 6).^{54,182,184,185}

The floatation technique is also used along with these deinking agents to purify and extract cellulose from waste papers. Air bubbles rise through the liquid in the tank with the suspended contaminant particles and waste paper pulp during the floatation deinking process. As the bubbles rise, ink clumps

Table 6 Common deinking agents and their parameters used in the extraction process of cellulose from waste paper

Sl no.	Deinking and purifying reagents	Strengths	Duration	Temperature	References
1	NaOH	5% (w/v)	Not defined	100 °C	54
	NaClO	2% (v/v)			
2	NaOH	2% (w/w)	30 min	53–57 °C	181
	Na ₂ SiO ₃	2% (w/w)			
3	H ₂ O ₂	1% (w/w)			
4	NaOH	0.5 and 1.0 M	5 h	Room temperature	184
	NaClO ₂	0.5, 1.0, and 2.0 M	1 h	75 °C	
5	NaOH	2.5% (w/w)	35 min	53–57 °C	183
	Na ₂ SiO ₃	2.25% (w/w)			
	H ₂ O ₂	0.50% (w/w)			
	NaClO ₂	1% (w/v)	1 h	75 °C	
	KOH	3.5% (w/v)	2 h	95 °C	
6	NaOH	1.5% (w/v)	30 min	Not defined	185
	H ₂ O ₂	3% (w/v)			
	Na ₂ SiO ₃	5% (w/v)			
	SDBS	1.5% (w/v)			
7	NaOH	1.2% (w/v)	1 h	45 °C	14
	Na ₂ SiO ₃	1.8% (w/v)			
	C ₁₈ H ₃₄ O ₂	0.9% (w/v)			
	H ₂ O ₂	0.8% (w/v)	50 min		
8	NaOH	5% (w/v)	2 h	125 °C	182
	NaClO	2% (w/v)	2 h	125 °C	
9	NaOH	2% (w/v)	2 h	90 °C	186
	NaClO ₂	Not defined	1 h	75 °C	
	KOH	2% (w/v)	2 h	90 °C	
10	NaOH	2% (w/v)	3 h	100 °C	187
	NaClO	2% (w/v)	1 h	70 °C	
11	CH ₃ COOH	Not defined	1 h	70 °C	



and hydrophobic impurities are gathered. After that, the adhered particles are shifted to a layer of foam, from which they can be readily removed.¹⁸¹ Tween-80 (0.1% w/w, 45 ± 2 °C for 7–12 min), commercial ISTEMUL 780 (0.1%), and sodium-4-polystyrene sulfonate (0.9%) are some floating agents used to form the froth layer.^{14,181,183,188} The airflow rate can be 10 L min⁻¹ and a pressure of 3 bar.¹⁴ Besides the flotation tank, mechanical agitation can be applied by a hydropulper or a repulper with a rate of 800–1000 rpm. This mechanical force, along with flotation and deinking agents, helps the ink fall off the waste paper and wash away other impurities like lignin and hemicellulose. Thus, pure cellulose is extracted from used papers.^{183,185}

5.2.2 Extraction of cellulose from waste fabric. Sample preparation: Supercritical CO₂ (scCO₂) is applied to clean and sterilize wasted cotton cloths, and a moderate temperature is maintained to remove microorganisms and impurities. Alkaline pulping: NaOH is used in a 1 : 20 ratio to remove lignin in this stage. This stage is important because it also helps it helps remove pectin and hemicellulose.⁵⁵ Bleaching: hydrogen peroxide (H₂O₂) is used for decolorization of the pulped fiber. This step helps dissolve lignin and hemicellulose, enhancing the cellulose yield. Acid hydrolysis: 64 wt% H₂SO₄ is used in this step.²

Vanzetto *et al.* used cotton fabric (100% natural raw cotton) waste and polyester fabric (50% polyester fiber + 50% treated natural cotton fiber) as the source of cellulose. They cut the waste sample into pieces of 1 cm × 1 cm. The sample was treated by ultrafine friction milling for 6 hours after being submerged in water for 24 hours. They oxidized the milled textile residue with 2,2,6,6-tetramethylpiperidine-1-oxyl (TEMPO). TEMPO reagent was mixed with distilled water to prepare the initial solution. The textile sample was mixed with the initial solution, in which NaBr (99.9% w/w) and NaClO (12% v/v) were mixed. The pH of this solution was kept in the range of 10 to 10.5 with the help of 0.1 M NaOH solution. The mixture was stirred for 20 minutes after 5 mL of ethanol was added to it. The oxidized cellulose was separated by centrifuging.¹³

S. Thambiraj and D. Ravi Shankaran used industrial waste cotton to extract cellulose, convert the extracted cellulose fiber into cellulose microcrystals, and finally into cellulose nanocrystals. They cut the cotton sample into pieces and washed it with hot water. The washed cotton was then dried in an oven for 2 hours. The cotton sample was then treated by alkali hydrolysis. The cotton was heated under continuous stirring in 20% NaOH solution for 4 hours at 40–60 °C. Then water was added to the solution to neutralize the pH value. The neutral suspension was filtered, and the filtrate underwent hydrolysis to remove hemicellulose and lignin. 500 mL of 60% sulfuric acid was used in this acid hydrolysis. After the hydrolysis for 8 hours at 50–60 °C, the cellulose formed a white slurry. Again, water was added to this slurry to make it neutral. It was kept for 12 hours to settle down. After settling, the slurry was rewashed. Cellulose microcrystals were isolated from this slurry by centrifuging the suspension at 5000 rpm, forwarded by drying in an oven overnight at 60 °C, and purified with acetone.¹⁸⁹

Table 7 Preparation method conditions for cellulose fiber from textile cotton waste

Sl no.	Sample preparation			Alkaline treatment			Bleaching			Acidic treatment			References
	Chemicals	Time	Temp. (°C)	Chemicals	Time	Temp. (°C)	Chemicals	Time	Temp. (°C)	Chemicals	Time	Temp. (°C)	
1	85 wt% citric acid	—	100	1 M NaOH	—	—	—	—	—	—	—	—	190
2	—	—	—	—	—	—	NaClO ₄ + NaCl NaClO ₂ + H ₂ O ₂ + NaCl	36 h 24 h	25 25	60 wt% H ₂ SO ₄	1 h	25	191
3	—	—	—	3% NaOH	6 h	Boil	0.6% NaClO	30 min	Boil	68% (w/w) HNO ₃ 37% (w/w) HCl	1 h	60	192
4	—	—	—	NaOH	4 h	25	—	—	—	64% H ₂ SO ₄	1 h	45	193
5	Hot water	—	—	26% NaOH	90 min	170	2% NaClO ₂ + 3% CH ₃ COOH	120 min	70	5% oxalic acid	6 h	—	55
6	Supercritical carbon dioxide	1 h	60	10 wt% (NaOH)	3 h	80	1.5% NaOH + 1% H ₂ O ₂ 1% NaClO ₂ + 3% CH ₃ COOH	90 min 90 min	70 60	64 wt% H ₂ SO ₄	1 h	45	2
7	Deionized water	10 min	25	10 wt% NaOH	2 h	70	1.5% (wt%) H ₂ O ₂	—	—	98 wt% H ₂ SO ₄ + 37 wt% HCl	7 h	55	194
8	Water	—	—	10% (w/w) NaOH	2 h	70	35% H ₂ O ₂	3 h	45	35% w/w H ₂ SO ₄	1 h	40	195



In Table 7, the sample was prepared using deionized water, supercritical CO₂, and citric acid, and the temperature was kept between 60 and 100 °C. Different NaOH concentrations are employed in alkaline treatment. When combined with 3% CH₃COOH and NaCl, NaClO₄, and H₂O₂, it acts as a bleaching agent. In the acidic treatment, several amounts of H₂SO₄, HNO₃, and HCl are often used.

Chemical agents like NaClO, KOH, and Na₂SiO₃ pose environmental risks due to toxicity and alkaline waste, while H₂O₂ and oleic acid are greener alternatives. Proper reagent selection and wastewater management are essential for sustainable cellulose extraction.

5.2.3 Extraction of cellulose from plant sources. Pre-hydrolysis: first, the raw materials are washed with distilled water and cut into small pieces. Sometimes, toluene/ethanol (2 : 1, v/v) is used to remove wax, phenolics, pigments, and oils.⁵² Then NaOH or other alkali aqueous solution is used under a mechanical stirrer to remove other constituents present in the pulp.⁴⁹ Pulping and Bleaching: there are two types of pulping treatment. Firstly, alkaline treatment, and secondly, acidic treatment. In alkaline treatment, plant materials are treated with an alkaline solution, typically sodium hydroxide, which helps to break down lignin from the cell wall.¹⁹⁶ KOH, KMnO₄, K₂Cr₂O₇, Na₂S, *etc.*, are also used in this step. The cellulose extraction process is described in Fig. 5. Then, the bleaching agent H₂O₂ is used to remove lignin and other non-cellulosic components.¹⁹⁷ We can perform an additional bleaching step using another agent like sodium hypochlorite (NaClO) or sodium perborate (NaBO₃ · nH₂O) to achieve a higher degree of purity and whiteness. An acidic treatment sometimes follows bleaching steps to neutralize the alkaline residues and further purify the cellulose. Typically, H₂SO₄ is used in this step.¹⁹⁸

Anuj Kumar and Yuvraj Singh Negi used sugarcane to extract cellulose nanocrystallites.¹⁹⁹ They first extracted the cellulose nanofibers by following the method done by others. This process requires less time for production than the conventional processes. At first, lignin was removed from the sample with the help of sodium chlorite solution. After treatment with sodium chlorite, the resultant white substance was treated with 3 wt%

and 6 wt% of potassium hydroxides at 80 °C for 2 hours to leach hemicellulose, pectin, and starch. After this, the purified cellulose fiber was soaked in distilled water and placed in an ultrasonic generator at 20–25 kHz. After 30 minutes of ultrasonication, the nanofibers of cellulose were isolated. Cellulose nanocrystals were then extracted from cellulose nanofibers by acid hydrolysis. This hydrolysis was done with the help of sulfuric acid (64% w/w) solution at 45 °C for 60 minutes to isolate the cellulose nanocrystals from cellulose microcrystals, they used a method similar to Anuj Kumar and Yuvraj Singh Negi.¹⁹⁹ Except, they heated the microcrystals with the sulfuric acid solution for 30–180 minutes, and the solution was centrifuged for 30 minutes.¹⁸⁹ Bibin Mathew Cheriana *et al.* used pineapple leaves as the source of cellulose.²⁰⁰

To scale up cellulose production in the industrial sector and increase production efficiency, Sakinul Islam *et al.* used the high-pressure process (HPP) and low-pressure process (LPP). They used rice husk from the paddy mill as the source of cellulose. The delignification process was done under LPP and HPP. They concluded that removing amorphous components like lignin, hemicellulose, *etc.*, was more efficient in HPP. The cellulose content was higher (93.68%) in HPP than in LPP (75.23%).²⁰¹

Hemmati, F. *et al.* used walnut shells as the cellulose fiber source. They slightly modified the method proposed by Bano and Negi to extract cellulose from the walnut shell. The walnut shell was ground and sieved before undergoing the dewaxing process. They used a methanol and benzene solution (ratio of 20 : 80) for 6 hours. They used a 1 M sodium hydroxide solution under continuous stirring for 4 hours at 85 °C to remove hemicellulose. After rinsing with distilled water several times, they used acetic acid and sodium chlorite to maintain the pH level at 3–4.²⁰²

Xiao-Feng Sun and Run-Cang Sun used a chlorine-free method to extract cellulose from straw. This method is more environmentally friendly than other conventional methods. They dewaxed dried straw in a toluene-ethanol solution. The dewaxed straw was then preheated with NaOH in 60% methanol (0.5 M, 60 °C, 2.5 hours). Then it was post-treated with 2% H₂O₂ and 0.2% TAED (tetra acetylene diamine) (48 °C, pH

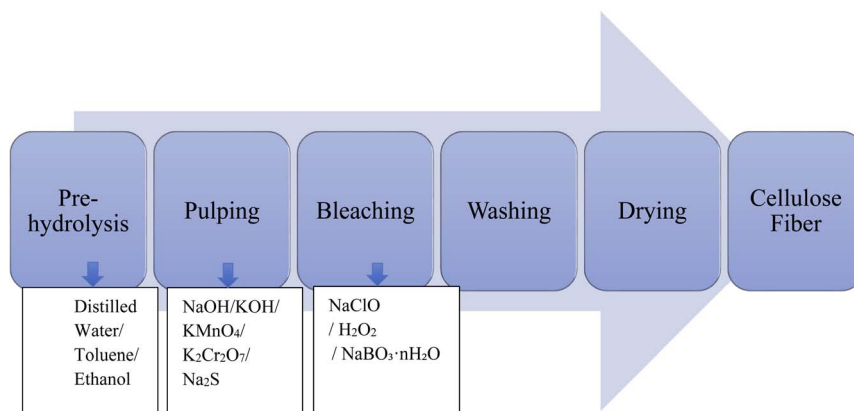


Fig. 5 Flow sheet of the production of cellulose fiber from the plant source.



Table 8 Extraction conditions of cellulose from different plant sources

Sl no.	Sources	Cellulose (%)	Pre-hydrolysis			Bleaching			Pulping			Ref.	
			Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time		
1	Rice husk	35	5 wt% NaOH	Boil	24 h	1% (w/v) NaClO ₂	Boil	2 h	5% (w/v) Na ₂ SO ₄ 18% (w/v) KOH 75% (wt) H ₂ SO ₄ 10 M H ₂ SO ₄ centrifugation at 10 000 rpm	— 25 — 10	1 h 48 h 10 min 10	1	
2	Rice husk	33	4 wt% NaOH	Reflux	2 h	Buffer solution of CH ₃ COOH, aq. Chlorite	100–130	4 h					204
3	Rice husk	36–40	5 wt% NaOH	120	45 min	NaClO ₂ + CH ₃ COOH	70	5 h	5% H ₂ SO ₄ + 5% H ₂ O ₂ + 25% CH ₃ COOH 10% HNO ₃ + 5% H ₂ O ₂ + 25% CH ₃ COOH	120	2 h	205	
4	Rice husk	~35	Deionized water	50	24 h	—	—	—	4% (w/w) H ₂ SO ₄ 5% (w/w) NaOH 3% (w/w) NaCl 18% NaOH 0.5, 1.5, 2.75 and 4% NaOH	Reflux Reflux 75 170 120	2 h 2 h 4 h 3 h 15, 30, 45 min	88	
5	Rice straw	30–60	2 wt% NaOH	170	3 h	NaClO ₂ , CH ₃ COOH	—	—					24
6	Sugarcane bagasse	40–50	C ₂ H ₅ OH and deionized water	100	1.5 h	1% NaOCl	95	60 min					25
7	Sugarcane bagasse	40–50	C ₂ H ₅ OH and deionized water	100	1.5 h	NaOH–H ₂ O ₂	105	24 h	Dilute H ₂ SO ₄ (0.5, 2.5, 5%)	—	15–30 min	25	
8	Cotton stalk	—	0.1% H ₂ SO ₄	160	30 min	10% NaClO, 2.2% H ₂ O ₂	60	60	14–20% NaOH + Na ₂ S	170	90 min	26	
9	Sisal fiber	50–74	0.1 M NaOH in 50% volume	45	3 h	0.5%, 1%, 2%, 3% H ₂ O ₂	45	3 h	10% NaOH – 1% Na ₂ B ₄ O ₇ ·10H ₂ O 70% HNO ₃ + 80% HAc	28 120	15 h 15 min	27	
10	Sisal fiber	50–74	C ₂ H ₅ OH	45	3 h	0.7% NaClO ₂	Boil	2 h	17.5% NaOH	125	4 h	27	
11	Leaves (<i>Pandanus tectorius</i>)	37.3 ± 0.6	Stagnant water	100	15	1.7% NaClO ₂	125	4 h	4% NaOH	125	4 h	28	
12	Kenaf	—	—	—	—	Acetate buffer (NaOH in CH ₃ COOH) + NaClO ₂	90	4 h	4% NaOH	90	3 h	29	
13	Kenaf stalk	56.81	NaOH	—	—	Alkaline–H ₂ O ₂ 50% purify	85	2 h	95–98% purified, 4% H ₂ SO ₄ 0.02% KMnO ₄ 0.02% K ₂ Cr ₂ O ₇	140 25 25	1 h 20 min 2 h	29	

Table 8 (Contd.)

Sl no.	Sources	Pre-hydrolysis			Bleaching			Pulping			Ref.	
		Cellulose (%)	Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)		Time
14	Ramie plant	—	Deionized water	Sundry	3 days	5% NaClO ₂ + CH ₃ COOH	170	120 min	18% NaOH	170	120 min	206
15	Jute	60.79	2 wt% NaOH	60	2 days	4% KOH	80	60 min	—	—	—	—
16	Unripe coconut husk	32.5	2 wt% NaOH	80	2 h	30% H ₂ O ₂	25	Overnight	27.7% H ₂ SO ₄	45	30 min	30
17	Coconut coil	—	60% w/w C ₂ H ₅ OH	150	4 h	NaClO ₂ in Glacial acetic acid	60–70	—	0.05 N HNO ₃	70	1 h	207
18	Pineapple crown leaves	79–83	1 M NaOH	80	1 h	3% H ₂ O ₂ + 4% NaOH	50	180 min	70% C ₂ H ₅ OH	—	—	31
19	Pineapple leaves	71.5	Deionized water	80	—	10% NaClO	—	—	3 M H ₂ SO ₄	45	1, 2, 3 h	32
20	Pineapple leaves	81.27	2% detergent solution	70	—	10% NaClO	100	30	2% NaOH	80	3 h	208
21	Banana peel	—	1% potassium metabisulfite	60	24	17.5% NaOH	80	1 h	20% NaOH + 0.1% anthraquinone	170	1.5 h	34
22	Alfa grass	—	3 N NaOH	100	2 h	1% NaClO ₂ + 10% CH ₃ COOH	70	1 h	—	—	—	—
23	Municipal grass	—	Distilled water	100	60 min	50% NaClO	80	48 h	50% v/v H ₂ SO ₄	70	30 min	35
24	African napier grass	47.1	Toluene-ethanol (2 : 1 v/v)	110	6 h	5% (v/v) H ₂ O ₂ + 1.3% NaOH + 0.7% NaClO ₂	80	90 min	4% NaOH	Reflux	90 min	36
25	Native yellow thatching grass	29.64 ± 0.81	Toluene-ethanol (2 : 1 v/v)	110	4 h	NaClO ₂ + CH ₃ COOH + 2% Na ₂ S	100	2 h	17.5% NaOH	20	45	37
26	Sabai grass	>55	Water	Sundry	3–4 days	NaClO ₂ + CH ₃ COOH	95	6 h	10% NaOH	100	4 h	209
27	Bamboo	—	Toluene-ethanol (2 : 1 v/v)	250	2 h (10–12) cycles	H ₂ O ₂ + 99.8% glacial acetic acid	130	3 h	6% NaOH	80	2 h	38
28	Barks of mulberry (<i>Morus alba</i> L.)	37.38 ± 2.31	1 (w/v) % NaOH	80	2 h	35% H ₂ O ₂ + 99.8% CH ₃ COOH in presence of TiO ₂	130	2 h	6% NaOH	80	2 h	39
29	Peel of prickly pear fruits	27	38 : 62 (v/v) Toluene-ethanol	Reflux	24 h	0.7 (v/v) % NaClO ₂ with acetate buffer + NaOH-glacial acetate acid	80	1.5 h	1 w/v% NaOH + 1 w/v% Na ₂ S and a bath ratio of 1 : 30	80 and 130 respectively	1.5 h	40
30	Wheat straw	45.70 ± 0.18	2% solution of NaOH	200 ± 5	Over night	8 (v/v) % H ₂ O ₂	25	Overnight	0.5% ammonium oxalate	60	2 h	210
			10–12 wt% NaOH	200 ± 5	4 h	—	—	—	0.05 N HCl	80	21 h	
									2% NaOH	80	2 h	
									10% HCl (1 N) solution	60 ± 1	5 h	41





Table 8 (Contd.)

Sl no.	Sources	Cellulose (%)	Pre-hydrolysis			Bleaching			Pulping			Ref.
			Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	
31	<i>Luffa cylindrica</i>	—	4% (w/w) NaOH	80	2 h	—	—	—	45% H ₂ SO ₄	50	40 min	48
32	Corn cob	31.2 ± 3.1	2% (w/w) NaOH	100	4 h	Acetate buffer (NaOH + glacial acetic acid), 1.7 wt% NaClO ₂	80	6 h	9.17 M H ₂ SO ₄	45	30, 60, 90 min	42
33	Poplar trees wood	—	2:1 (v/v) mixture of benzene/ethanol	90	6 h	NaClO ₂	75	1 h	3 wt% KOH 6 wt% KOH	80 80	2 h 2 h	43
34	Soybean	—	17.5% NaOH	25	2 h	Chlorine dioxide solution	50	1 h	1 M HCl 2% (w/w) NaOH	80	2 h	44
35	Lemon peel	—	—	—	—	NaOH and H ₂ O ₂	High temp	—	2.5 N HCl	Reflux	10 h	45
36	Henequen fiber	60	0.4% H ₂ SO ₄	Boil	—	3.5% NaClO	30	—	20% NaOH	25	—	211
37	Jackfruit (<i>Artocarpus heterophyllus</i>)	—	2% NaOH	50	180 min	3% H ₂ O ₂ + 4% NaOH	50	180 min	52% (w/w) H ₂ SO ₄	45	120 min	209
38	Jackfruit peel	20.08 ± 0.05	1 M NaOH	60	2 h	1.5% NaClO ₂	70	2 h	65% H ₂ SO ₄	37	1 h	46
39	Palm oil empty fruit bunches	36.67	Soaked in distilled water	25	24 h	—	—	—	55%, 60%, and 64% H ₂ SO ₄	35 and 45	3 h and 6 h	47
40	Onion skin	81	Distilled water	85	2 h	Acetate buffer + 1.7% aq. Chlorite	80	2h	2% NaOH	80	2 h	212
41	Carrot peel	41.1 ± 1.1	Water + air oven	105	24 h	0.7% NaClO ₂ + 5% CH ₃ COOH + 5% Na ₂ S	Boil	5h	17.5% NaOH	20	45	49
42	Pumpkin peel	—	2 wt% NaOH	100	4 h	0.5 M NaOH + 2% (v/v) H ₂ O ₂	55	5 h	1-Butyl-3-methylimidazolium chloride	90	24 h	50
43	Tomato peel	—	Toluene/ethanol (2:1, v/v)	70	24 h	1.4% NaClO ₂ NaOH/4% H ₂ O ₂	70 90	5 h 5 h	5% KOH NaOH	90 45	2 h 6 h	51
44	Potato residues	24.86	Detonized water	Boil	3 min	10% (v/v) H ₂ O ₂	70	1.5 h	7% NaOH	70	1 h	52
45	Abaca pulp	66.43	2 wt% of sodium chlorites + KCl, HCl buffer solution	—	Over night	NaClO ₂	—	—	Na ₂ CO ₃ -NaHCO ₃ buffer solution + NaBr (1.0%) + TEMPO (0.16%)	—	—	53
46	<i>Juncus effusus</i>	40	Distilled water	60	Over night	H ₂ O ₂ , NaOCl, NaBO ₃ ·4H ₂ O	95	45 min	8 M NaOH	100	3 h	197



Table 8 (Contd.)

Sl no.	Sources	Cellulose (%)	Pre-hydrolysis			Bleaching			Pulping			Ref.
			Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	Chemicals	Temp. (°C)	Time	
47	Pine trees	—	Deionized water	—	1 h	30% (w/w) H ₂ O ₂ 1 M H ₂ SO ₄ + 1 M, 10% (v/v) 1-Ethyl-3- methylimidazolium chloride	50 95	1 h 1 h	2% (w/v) NaOH	120	1 h	55
48	Orange peel	—	Ethanol and toluene	—	—	0.7% (w/v) NaClO ₂	80	2 h	NaOH/KOH	Reflux	2 h	179

11.8, 12 hours). The crude cellulose was purified with 80% acetic acid and 70% nitric acid.^{20,3} Their method creates less pollution than the conventional methods, but it is more time-consuming and costly. The size distribution of cellulose fiber was lower in the conventional method than in the chlorine-free method.²⁷

In Table 8, carrot peel (81%) and pineapple leaves (81.27%) have the highest cellulose content. Pretreatment of pineapple leaves involves a 2% detergent solution at 70 °C, followed by bleaching with 10% NaClO at 100 °C and 17.5% NaOH. 2% NaOH is applied for three hours at 80 °C during the pulping stage. Carrot peel cellulose is extracted using an aqueous acetic buffer containing 1.7% aq. The bleaching step uses a chlorite solution, while the pulping step uses 2% NaOH at 80 °C for three hours. Jackfruit peel contains the least quantity of cellulose (20.08%). This source is pretreated with 1 M NaOH and bleached with 1.5% NaClO₂ at 70 °C for two hours. In the pulping stage, 65% H₂SO₄ is used for 1 h at 37 °C.

6. Conclusion

Utilizing natural and waste-derived resources, such as crab shells, plant leftovers, textile scraps, and newspaper waste, to extract cellulose, chitin, and chitosan has become more important due to the increasing demand for eco-friendly and sustainable products. The basic chemical and biological extraction methods of chitin and chitosan have been described in this study, focusing on the steps of demineralization, deproteinization, and deacetylation. Because of their increased production and efficiency, chemical methods continue to govern industrial applications and pose environmental challenges. On the other hand, although being ecologically safe, biological approaches are limited by their higher prices, longer processing times, and lower efficiency. A potential approach for recovering plentiful textile and agricultural waste is cellulose extraction, which involves a series of steps such as pre-hydrolysis, pulping, bleaching, and washing. Reagent use and energy input, however, continue to be significant issues that necessitate more environmentally friendly options. Future studies should focus on developing microbial strains and enzyme engineering to enhance the efficiency and reduce the cost of biological extraction methods. Incorporating sustainable reagents and improving hybrid approaches that combine the advantages of chemical and biological processes must also be priorities. These developments will widen the possibility for greater industrial use and significantly support a circular economy by bridging the gap between the generation of waste and resource recovery.

Data availability

Data will be made available on request from authors.

Conflicts of interest

There are no conflicts to declare.

References

- 1 D. Onoja, I. Ahemen and T. Iorfa, Synthesis and characterization of cellulose based nanofibres from rice husk, *J. Appl. Phys.*, 2019, **11**(2), 80–87.
- 2 S. Mohamed, *et al.*, Recycling Waste Cotton Cloths for the Isolation of Cellulose Nanocrystals: A Sustainable Approach, *Polymers*, 2021, **13**(4), 626, DOI: [10.3390/polym13040626](https://doi.org/10.3390/polym13040626).
- 3 J. Chakravarty and T. A. Edwards, Innovation from waste with biomass-derived chitin and chitosan as green and sustainable polymer: A review, *Energy Nexus*, 2022, **8**, 100149, DOI: [10.1016/j.nexus.2022.100149](https://doi.org/10.1016/j.nexus.2022.100149).
- 4 V. Sieber, M. Hofer, W. M. Brück, D. Garbe, T. Brück, and C. A. Lynch, ChiBio: An Integrated Bio-refinery for Processing Chitin-Rich Bio-waste to Specialty Chemicals, in *Grand Challenges in Marine Biotechnology*, ed. P. H. Rampelotto and A. Trincone, Springer International Publishing, Cham, 2018, pp. 555–578, DOI: [10.1007/978-3-319-69075-9_14](https://doi.org/10.1007/978-3-319-69075-9_14).
- 5 F. Gao, *et al.*, Simultaneous nutrient removal and biomass/lipid production by *Chlorella* sp. in seafood processing wastewater, *Sci. Total Environ.*, 2018, **640–641**, 943–953, DOI: [10.1016/j.scitotenv.2018.05.380](https://doi.org/10.1016/j.scitotenv.2018.05.380).
- 6 J. Chakravarty, C.-L. Yang, J. Palmer and C. Brigham, Chitin extraction from lobster shell waste using microbial culture-based methods, *Appl. Food Biotechnol.*, 2018, **5**, 141–154, DOI: [10.22037/afb.v%vi%i.20787](https://doi.org/10.22037/afb.v%vi%i.20787).
- 7 N. Yan and X. Chen, Sustainability: Don't waste seafood waste, *Nature*, 2015, **524**(7564), 155–157, DOI: [10.1038/524155a](https://doi.org/10.1038/524155a).
- 8 I. Suyambulingam, *et al.*, Chitosan Biopolymer and Its Nanocomposites: Emerging Material as Adsorbent in Wastewater Treatment, *Adv. Mater. Sci. Eng.*, 2023, **2023**, 1–20, DOI: [10.1155/2023/9387016](https://doi.org/10.1155/2023/9387016).
- 9 B. Moussian, Chitin: Structure, Chemistry and Biology, in *Targeting Chitin-Containing Organisms*, ed. Q. Yang and T. Fukamizo, Springer Singapore, Singapore, 2019, pp. 5–18, DOI: [10.1007/978-981-13-7318-3_2](https://doi.org/10.1007/978-981-13-7318-3_2).
- 10 S. Islam, M. A. R. Bhuiyan and M. N. Islam, Chitin and Chitosan: Structure, Properties and Applications in Biomedical Engineering, *J. Polym. Environ.*, 2017, **25**(3), 854–866, DOI: [10.1007/s10924-016-0865-5](https://doi.org/10.1007/s10924-016-0865-5).
- 11 E. Bågenholm-Ruuth, M. Sanchis-Sebastiá, N. Hollinger, A. Teleman, P. T. Larsson and O. Wallberg, Transforming post-consumer cotton waste textiles into viscose staple fiber using hydrated zinc chloride, *Cellulose*, 2024, **31**(2), 737–748, DOI: [10.1007/s10570-023-05646-2](https://doi.org/10.1007/s10570-023-05646-2).
- 12 C. Felgueiras, N. G. Azoia, C. Gonçalves, M. Gama and F. Dourado, Trends on the Cellulose-Based Textiles: Raw Materials and Technologies, *Front. Bioeng. Biotechnol.*, 2021, **9**, 608826, DOI: [10.3389/fbioe.2021.608826](https://doi.org/10.3389/fbioe.2021.608826).
- 13 A. B. Vanzetto, L. V. R. Beltrami and A. J. Zattera, Textile waste as precursors in nanocrystalline cellulose synthesis, *Cellulose*, 2021, **28**(11), 6967–6981, DOI: [10.1007/s10570-021-03982-9](https://doi.org/10.1007/s10570-021-03982-9).
- 14 M. Hietala, K. Varrio, L. Berglund, J. Soini and K. Oksman, Potential of municipal solid waste paper as raw material for production of cellulose nanofibres, *Waste Manage.*, 2018, **80**, 319–326, DOI: [10.1016/j.wasman.2018.09.033](https://doi.org/10.1016/j.wasman.2018.09.033).
- 15 A. A. Sundarraj and T. V. Ranganathan, A review on cellulose and its utilization from agro-industrial waste, *Drug Invent. Today*, 2018, **10**(1), 89–94.
- 16 M. J. Ioelovich, Microcellulose vs nanocellulose—a review, *World J. Adv. Eng. Technol. Sci.*, 2022, **5**(2), 1–15.
- 17 D. Klemm, *et al.*, Nanocelluloses: A New Family of Nature-Based Materials, *Angew. Chem., Int. Ed.*, 2011, **50**(24), 5438–5466, DOI: [10.1002/anie.201001273](https://doi.org/10.1002/anie.201001273).
- 18 A. Ferrer, L. Pal and M. Hubbe, Nanocellulose in packaging: Advances in barrier layer technologies, *Ind. Crops Prod.*, 2017, **95**, 574–582, DOI: [10.1016/j.indcrop.2016.11.012](https://doi.org/10.1016/j.indcrop.2016.11.012).
- 19 H. Ao and X. Xun, Bacterial Nanocellulose: Methods, Properties, and Biomedical Applications, in *Nanocellulose-Sources, Preparations, and Applications*, IntechOpen, 2024.
- 20 S. More, V. Shete, and A. Pethe, An overview of nanocrystalline cellulose: A brief review on experimental, make-up, chemical modification and applications, presented at the *AIP Conference Proceedings*, AIP Publishing, 2024.
- 21 K. Shaikh, W. A. Khan, M. S. N. Kazi, and M. N. M. Zubir, Nanocellulose: Fundamentals and Applications, in *Nanocellulose-Sources, Preparations, and Applications*, IntechOpen, 2024.
- 22 A. A. B. Omran, *et al.*, Micro- and Nanocellulose in Polymer Composite Materials: A Review, *Polymers*, 2021, **13**(2), 231, DOI: [10.3390/polym13020231](https://doi.org/10.3390/polym13020231).
- 23 H. S. Hafid, F. N. Omar, J. Zhu and M. Wakisaka, Enhanced crystallinity and thermal properties of cellulose from rice husk using acid hydrolysis treatment, *Carbohydr. Polym.*, 2021, **260**, 117789, DOI: [10.1016/j.carbpol.2021.117789](https://doi.org/10.1016/j.carbpol.2021.117789).
- 24 N. A. M. Razali, *et al.*, Comparative Study on Extraction of Cellulose Fiber from Rice Straw Waste from Chemo-Mechanical and Pulping Method, *Polymers*, 2022, **14**(3), 387, DOI: [10.3390/polym14030387](https://doi.org/10.3390/polym14030387).
- 25 G. T. Melesse, F. G. Hone and M. A. Mekonnen, Extraction of Cellulose from Sugarcane Bagasse Optimization and Characterization, *Adv. Mater. Sci. Eng.*, 2022, **2022**, 1–10, DOI: [10.1155/2022/1712207](https://doi.org/10.1155/2022/1712207).
- 26 M. Li, B. He and L. Zhao, Isolation and characterization of microcrystalline cellulose from cotton stalk waste, *BioResources*, 2019, **14**(2), 3231–3246, DOI: [10.15376/biores.14.2.3231-3246](https://doi.org/10.15376/biores.14.2.3231-3246).
- 27 J. I. Morán, V. A. Alvarez, V. P. Cyras and A. Vázquez, Extraction of cellulose and preparation of nanocellulose from sisal fibers, *Cellulose*, 2008, **15**(1), 149–159, DOI: [10.1007/s10570-007-9145-9](https://doi.org/10.1007/s10570-007-9145-9).
- 28 R. M. Sheltami, I. Abdullah, I. Ahmad, A. Dufresne and H. Kargarzadeh, Extraction of cellulose nanocrystals from mengkuang leaves (*Pandanus tectorius*), *Carbohydr. Polym.*, 2012, **88**(2), 772–779, DOI: [10.1016/j.carbpol.2012.01.062](https://doi.org/10.1016/j.carbpol.2012.01.062).
- 29 A. Guo, Z. Sun and J. Satyavolu, Impact of chemical treatment on the physiochemical and mechanical properties of kenaf fibers, *Ind. Crops Prod.*, 2019, **141**, 111726, DOI: [10.1016/j.indcrop.2019.111726](https://doi.org/10.1016/j.indcrop.2019.111726).



- 30 N. Kasyapi, V. Chaudhary and A. K. Bhowmick, Bionanowhiskers from jute: Preparation and characterization, *Carbohydr. Polym.*, 2013, **92**(2), 1116–1123, DOI: [10.1016/j.carbpol.2012.10.021](https://doi.org/10.1016/j.carbpol.2012.10.021).
- 31 T. A. Cevanti, *et al.*, Cellulose Fiber from Coconut Coir for Development of Dental Composite Filler, *J. Int. Dent. Med. Res.*, 2021, **14**(4), 1401–1406.
- 32 Fitriani, N. A. S. Aprilia and N. Arahman, Properties of nanocrystalline cellulose from pineapple crown leaf waste, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2020, **796**(1), 012007, DOI: [10.1088/1757-899X/796/1/012007](https://doi.org/10.1088/1757-899X/796/1/012007).
- 33 H. Amirulhakim, A. L. Juwono and S. Roseno, Isolation and characterization of Cellulose Nanofiber from Subang Pineapple Leaf Fiber waste produced using Ultrafine Grinding method, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2021, **1098**(6), 062067, DOI: [10.1088/1757-899X/1098/6/062067](https://doi.org/10.1088/1757-899X/1098/6/062067).
- 34 V. N. Krishnan and A. Ramesh, Synthesis and Characterization of Surface Modified Cellulose Nanofibers from Banana Peel, *IOSR J. Appl. Chem.*, 2017, **10**(01), 15–19, DOI: [10.9790/5736-1001021519](https://doi.org/10.9790/5736-1001021519).
- 35 S. Ben Cheikh, R. Ben Cheikh, E. Cunha, P. E. Lopes and M. C. Paiva, Production of cellulose nanofibers from Alfa grass and application as reinforcement for polyvinyl alcohol, *Plast. Rubber Compos.*, 2018, **47**(7), 297–305, DOI: [10.1080/14658011.2018.1479822](https://doi.org/10.1080/14658011.2018.1479822).
- 36 W. H. Danial, R. Mohd Taib, M. A. Abu Samah, R. Mohd Salim and Z. Abdul Majid, The valorization of municipal grass waste for the extraction of cellulose nanocrystals, *RSC Adv.*, 2020, **10**(69), 42400–42407, DOI: [10.1039/D0RA07972C](https://doi.org/10.1039/D0RA07972C).
- 37 K. O. Reddy, *et al.*, Extraction and characterization of cellulose single fibers from native african napier grass, *Carbohydr. Polym.*, 2018, **188**, 85–91, DOI: [10.1016/j.carbpol.2018.01.110](https://doi.org/10.1016/j.carbpol.2018.01.110).
- 38 A. Puri, R. Adhikari and R. Pandit, Mechanical and Structural Characterization of Resole Resin Composites Reinforced with Sabai Grass-Derived Cellulose Fibers, *J. Nepal Chem. Soc.*, 2024, **44**(2), 43–51, DOI: [10.3126/jncs.v44i2.68302](https://doi.org/10.3126/jncs.v44i2.68302).
- 39 F. K. Liew, *et al.*, Synthesis and Characterization of Cellulose from Green Bamboo by Chemical Treatment with Mechanical Process, *J. Chem.*, 2015, **2015**, 1–6, DOI: [10.1155/2015/212158](https://doi.org/10.1155/2015/212158).
- 40 R. Li, J. Fei, Y. Cai, Y. Li, J. Feng and J. Yao, Cellulose whiskers extracted from mulberry: A novel biomass production, *Carbohydr. Polym.*, 2009, **76**(1), 94–99, DOI: [10.1016/j.carbpol.2008.09.034](https://doi.org/10.1016/j.carbpol.2008.09.034).
- 41 A. Kaushik and M. Singh, Isolation and characterization of cellulose nanofibrils from wheat straw using steam explosion coupled with high shear homogenization, *Carbohydr. Res.*, 2011, **346**(1), 76–85, DOI: [10.1016/j.carres.2010.10.020](https://doi.org/10.1016/j.carres.2010.10.020).
- 42 H. A. Silvério, W. P. Flauzino Neto, N. O. Dantas and D. Pasquini, Extraction and characterization of cellulose nanocrystals from corn cob for application as reinforcing agent in nanocomposites, *Ind. Crops Prod.*, 2013, **44**, 427–436, DOI: [10.1016/j.indcrop.2012.10.014](https://doi.org/10.1016/j.indcrop.2012.10.014).
- 43 W. Chen, H. Yu, Y. Liu, P. Chen, M. Zhang and Y. Hai, Individualization of cellulose nanofibers from wood using high-intensity ultrasonication combined with chemical pretreatments, *Carbohydr. Polym.*, 2011, **83**(4), 1804–1811, DOI: [10.1016/j.carbpol.2010.10.040](https://doi.org/10.1016/j.carbpol.2010.10.040).
- 44 B. Wang and M. Sain, Isolation of nanofibers from soybean source and their reinforcing capability on synthetic polymers, *Compos. Sci. Technol.*, 2007, **67**(11–12), 2521–2527, DOI: [10.1016/j.compscitech.2006.12.015](https://doi.org/10.1016/j.compscitech.2006.12.015).
- 45 C. Rondeau-Mouro, B. Bouchet, B. Pontoire, P. Robert, J. Mazoyer and A. Buléon, Structural features and potential texturising properties of lemon and maize cellulose microfibrils, *Carbohydr. Polym.*, 2003, **53**(3), 241–252, DOI: [10.1016/S0144-8617\(03\)00069-9](https://doi.org/10.1016/S0144-8617(03)00069-9).
- 46 C. Trilokesh and K. B. Uppuluri, Isolation and characterization of cellulose nanocrystals from jackfruit peel, *Sci. Rep.*, 2019, **9**(1), 16709, DOI: [10.1038/s41598-019-53412-x](https://doi.org/10.1038/s41598-019-53412-x).
- 47 D. Setyaningsih, Uju, N. Muna, Isroi, N. B. Suryawan and A. A. Nurfauzi, Cellulose nanofiber isolation from palm oil Empty Fruit Bunches (EFB) through strong acid hydrolysis, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2018, **141**, 012027, DOI: [10.1088/1755-1315/141/1/012027](https://doi.org/10.1088/1755-1315/141/1/012027).
- 48 N. Follain, S. Belbekhouche, J. Bras, G. Siqueira, S. Marais and A. Dufresne, Water transport properties of bio-nanocomposites reinforced by *Luffa cylindrica* cellulose nanocrystals, *J. Membr. Sci.*, 2013, **427**, 218–229, DOI: [10.1016/j.memsci.2012.09.048](https://doi.org/10.1016/j.memsci.2012.09.048).
- 49 J.-W. Rhim, J. P. Reddy and X. Luo, Isolation of cellulose nanocrystals from onion skin and their utilization for the preparation of agar-based bio-nanocomposites films, *Cellulose*, 2015, **22**(1), 407–420, DOI: [10.1007/s10570-014-0517-7](https://doi.org/10.1007/s10570-014-0517-7).
- 50 T. Côto, I. Moura, A. de Sá, C. Vilarinho and A. V. Machado, Sustainable Materials Based on Cellulose from Food Sector Agro-Wastes, *J. Renewable Mater.*, 2018, **6**(7), 688–696, DOI: [10.32604/JRM.2018.00006](https://doi.org/10.32604/JRM.2018.00006).
- 51 F. Jiang and Y.-L. Hsieh, Cellulose nanocrystal isolation from tomato peels and assembled nanofibers, *Carbohydr. Polym.*, 2015, **122**, 60–68, DOI: [10.1016/j.carbpol.2014.12.064](https://doi.org/10.1016/j.carbpol.2014.12.064).
- 52 X. Liu, H. Sun, T. Mu, M. L. Fauconnier and M. Li, Preparation of cellulose nanofibers from potato residues by ultrasonication combined with high-pressure homogenization, *Food Chem.*, 2023, **413**, 135675, DOI: [10.1016/j.foodchem.2023.135675](https://doi.org/10.1016/j.foodchem.2023.135675).
- 53 A. Lapuz, S. Tsuchikawa, T. Inagaki, T. Ma and V. Migo, Production of Nanocellulose Film from Abaca Fibers, *Crystals*, 2022, **12**(5), 601, DOI: [10.3390/cryst12050601](https://doi.org/10.3390/cryst12050601).
- 54 W. H. Danial, Z. Abdul Majid, M. N. Mohd Muhid, S. Triwahyono, M. B. Bakar and Z. Ramli, The reuse of wastepaper for the extraction of cellulose nanocrystals, *Carbohydr. Polym.*, 2015, **118**, 165–169, DOI: [10.1016/j.carbpol.2014.10.072](https://doi.org/10.1016/j.carbpol.2014.10.072).
- 55 H. Nasution, *et al.*, Extraction and Isolation of Cellulose Nanofibers from Carpet Wastes Using Supercritical Carbon Dioxide Approach, *Polymers*, 2022, **14**(2), 326, DOI: [10.3390/polym14020326](https://doi.org/10.3390/polym14020326).



- 56 M. Rinaudo, Chitin and chitosan: Properties and applications, *Prog. Polym. Sci.*, 2006, **31**(7), 603–632.
- 57 I. Aranaz, *et al.*, Functional characterization of chitin and chitosan, *Curr. Chem. Biol.*, 2009, **3**(2), 203–230.
- 58 W. W. Ngah and L. Teong, Adsorption of dyes and heavy metal ions by chitosan composites: A review, *Carbohydr. Polym.*, 2011, **83**(4), 1446–1456.
- 59 M. Sathiyabama, G. Akila and R. E. Charles, Chitosan-induced defence responses in tomato plants against early blight disease caused by *Alternaria solani* (Ellis and Martin) Sorauer, *Arch. Phytopathol. Plant Prot.*, 2014, **47**(16), 1963–1973.
- 60 R. Jayakumar, M. Prabakaran, P. S. Kumar, S. Nair, T. Furuike and H. Tamura, Novel chitin and chitosan materials in wound dressing, *Biomed. Eng., Trends Mater. Sci.*, 2011, 3–24.
- 61 I. Siró and D. Plackett, Microfibrillated cellulose and new nanocomposite materials: a review, *Cellulose*, 2010, **17**, 459–494.
- 62 I. A. Ahmed, M. A. Mikail, N. Zamakshshari and A.-S. H. Abdullah, Natural anti-aging skincare: role and potential, *Biogerontology*, 2020, **21**, 293–310.
- 63 R. Muzzarelli, *et al.*, Filmogenic properties of chitin/chitosan, *Chitin Nat. Technol.*, 1986, 389–402.
- 64 I. A. Ahmed, M. A. Mikail, N. Zamakshshari and A.-S. H. Abdullah, Natural anti-aging skincare: role and potential, *Biogerontology*, 2020, **21**, 293–310.
- 65 V. S. Yeul and S. S. Rayalu, Unprecedented Chitin and Chitosan: A Chemical Overview, *J. Polym. Environ.*, 2013, **21**(2), 606–614, DOI: [10.1007/s10924-012-0458-x](https://doi.org/10.1007/s10924-012-0458-x).
- 66 J. Kumirska, *et al.*, Application of Spectroscopic Methods for Structural Analysis of Chitin and Chitosan, *Mar. Drugs*, 2010, **8**(5), 1567–1636, DOI: [10.3390/md8051567](https://doi.org/10.3390/md8051567).
- 67 G. A. F. Roberts, *Chitin Chemistry*, Macmillan Education UK, London, 1992, DOI: [10.1007/978-1-349-11545-7](https://doi.org/10.1007/978-1-349-11545-7).
- 68 E. Khor, Chitin: Fulfilling a Biomaterials Promise: Second Edition, *Biomaterials*, 2001, 3913–3915.
- 69 Crystalline Cellulose and Derivatives: Characterization and Structures, in *Springer Series in Wood Science*, ed. P. Zugenmaier, Springer-Verlag Berlin Heidelberg, Berlin, Heidelberg, 2008, DOI: [10.1007/978-3-540-73934-0](https://doi.org/10.1007/978-3-540-73934-0).
- 70 G. A. M. Ruiz and H. F. Z. Corrales, Chitosan, Chitosan Derivatives and their Biomedical Applications, in *Biological Activities and Application of Marine Polysaccharides*, ed. E. A. Shalaby, InTech, 2017, DOI: [10.5772/66527](https://doi.org/10.5772/66527).
- 71 C. V. Nikiforidis and E. Scholten, Polymer organogelation with chitin and chitin nanocrystals, *RSC Adv.*, 2015, **5**(47), 37789–37799, DOI: [10.1039/C5RA06451A](https://doi.org/10.1039/C5RA06451A).
- 72 K. Jellouli, O. Ghorbel bellaaj, H. Ayed, L. Manni and R. Agrebi, Alkaline-protease from *Bacillus licheniformis* MP1: Purification, characterization and potential application as a detergent additive and for shrimp waste deproteinization, *Process Biochem.*, 2011, **46**, 1248–1256, DOI: [10.1016/j.procbio.2011.02.012](https://doi.org/10.1016/j.procbio.2011.02.012).
- 73 M. L. Duarte, M. C. Ferreira, M. R. Marvão and J. Rocha, An optimised method to determine the degree of acetylation of chitin and chitosan by FTIR spectroscopy, *Int. J. Biol. Macromol.*, 2002, **31**(1–3), 1–8, DOI: [10.1016/S0141-8130\(02\)00039-9](https://doi.org/10.1016/S0141-8130(02)00039-9).
- 74 N. G. Kandile, H. T. Zaky, M. I. Mohamed, A. S. Nasr and Y. G. Ali, Extraction and Characterization of Chitosan from Shrimp Shells, *Open J. Org. Polym. Mater.*, 2018, **08**(03), 33–42, DOI: [10.4236/ojopm.2018.83003](https://doi.org/10.4236/ojopm.2018.83003).
- 75 R. Agrebi, A. Haddar, N. Hmidet, K. Jellouli and L. Manni, BSF1 fibrinolytic enzyme from a marine bacterium *Bacillus subtilis* A26: Purification, biochemical and molecular characterization, *Process Biochem.*, 2009, **44**, 1252–1259, DOI: [10.1016/j.procbio.2009.06.024](https://doi.org/10.1016/j.procbio.2009.06.024).
- 76 K. Panchal and M. Desai, Chitin: Production, Purification, and Characterization, *Biot. Elicitors*, Springer, 2022, pp. 87–99, DOI: [10.1007/978-1-0716-2601-6_11](https://doi.org/10.1007/978-1-0716-2601-6_11).
- 77 M. Ali, M. Shakeel and K. Mehmood, Extraction and characterization of high purity chitosan by rapid and simple techniques from mud crabs taken from Abbottabad, *Pak. J. Pharm. Sci.*, 2019, **32**(1), 171–175.
- 78 B. Buanasari, W. Sugiyono, N. Fitriani and S. Suryaningsih, Potential of Chitosan From Local Crab (*Portunus Pelagicus*) to Enhance Storability of *Musa Paradisiaca* L., *J. Bahan Alam Terbarukan*, 2019, **8**(1), 41–46, DOI: [10.15294/jbat.v8i1.16423](https://doi.org/10.15294/jbat.v8i1.16423).
- 79 S. Kumari, S. H. Kumar Annamareddy, S. Abanti and P. Kumar Rath, Physicochemical properties and characterization of chitosan synthesized from fish scales, crab and shrimp shells, *Int. J. Biol. Macromol.*, 2017, **104**, 1697–1705, DOI: [10.1016/j.ijbiomac.2017.04.119](https://doi.org/10.1016/j.ijbiomac.2017.04.119).
- 80 H. El Knidri, R. El Khalfaouy, A. Laajeb, A. Addaou and A. Lahsini, Eco-friendly extraction and characterization of chitin and chitosan from the shrimp shell waste via microwave irradiation, *Process Saf. Environ. Prot.*, 2016, **104**, 395–405, DOI: [10.1016/j.psep.2016.09.020](https://doi.org/10.1016/j.psep.2016.09.020).
- 81 M. Kim, *et al.*, Production of chitin and chitosan from the exoskeleton of adult two-spotted field crickets (*Gryllus bimaculatus*), *Entomol. Res.*, 2017, **47**(5), 279–285, DOI: [10.1111/1748-5967.12239](https://doi.org/10.1111/1748-5967.12239).
- 82 I. Younes, S. Hajji, V. Frachet, M. Rinaudo, K. Jellouli and M. Nasri, Chitin extraction from shrimp shell using enzymatic treatment. Antitumor, antioxidant and antimicrobial activities of chitosan, *Int. J. Biol. Macromol.*, 2014, **69**, 489–498, DOI: [10.1016/j.ijbiomac.2014.06.013](https://doi.org/10.1016/j.ijbiomac.2014.06.013).
- 83 I. Tsigos, A. Martinou, D. Kafetzopoulos and V. Bouriotis, Chitin deacetylases: new, versatile tools in biotechnology, Trends in Biotechnology, *Trends Biotechnol.*, 2000, **18**(7), 305–312, DOI: [10.1016/S0167-7799\(00\)01462-1](https://doi.org/10.1016/S0167-7799(00)01462-1).
- 84 Y. Zhao, R.-D. Park and R. A. A. Muzzarelli, Chitin Deacetylases: Properties and Applications, *Mar. Drugs*, 2010, **8**(1), 24–46, DOI: [10.3390/md8010024](https://doi.org/10.3390/md8010024).
- 85 S. (Gabriel) Kou, L. M. Peters and M. R. Mucalo, Chitosan: A review of sources and preparation methods, *Int. J. Biol. Macromol.*, 2021, **169**, 85–94, DOI: [10.1016/j.ijbiomac.2020.12.005](https://doi.org/10.1016/j.ijbiomac.2020.12.005).
- 86 I. Younes and M. Rinaudo, Chitin and Chitosan Preparation from Marine Sources. Structure, Properties and Applications, *Mar. Drugs*, 2015, **13**(3), 1133–1174, DOI: [10.3390/md13031133](https://doi.org/10.3390/md13031133).



- 87 S.-K. Kim, *Chitin, Chitosan, Oligosaccharides and Their Derivatives*, CRC Press, 2010.
- 88 R. Aranday-García, H. Saimoto, K. Shirai and S. Ifuku, Chitin biological extraction from shrimp wastes and its fibrillation for elastic nanofiber sheets preparation, *Carbohydr. Polym.*, 2019, **213**, 112–120, DOI: [10.1016/j.carbpol.2019.02.083](https://doi.org/10.1016/j.carbpol.2019.02.083).
- 89 H. Srinivasan, V. Kanayairam and R. Ravichandran, Chitin and chitosan preparation from shrimp shells *Penaeus monodon* and its human ovarian cancer cell line, PA-1, *Int. J. Biol. Macromol.*, 2018, **107**, 662–667, DOI: [10.1016/j.ijbiomac.2017.09.035](https://doi.org/10.1016/j.ijbiomac.2017.09.035).
- 90 A. Hosney, S. Ullah and K. Barčauskaitė, A Review of the Chemical Extraction of Chitosan from Shrimp Wastes and Prediction of Factors Affecting Chitosan Yield by Using an Artificial Neural Network, *Mar. Drugs*, 2022, **20**(11), 675, DOI: [10.3390/md20110675](https://doi.org/10.3390/md20110675).
- 91 M. Anand, P. Sathyapriya, M. Maruthupandy and A. Hameedha Beevi, Synthesis of chitosan nanoparticles by TPP and their potential mosquito larvicidal application, *Front. Lab. Med.*, 2018, **2**(2), 72–78, DOI: [10.1016/j.flm.2018.07.003](https://doi.org/10.1016/j.flm.2018.07.003).
- 92 T. K. Varun, *et al.*, Extraction of chitosan and its oligomers from shrimp shell waste, their characterization and antimicrobial effect, *Vet. World*, 2017, **10**(2), 170–175, DOI: [10.14202/vetworld.2017.170-175](https://doi.org/10.14202/vetworld.2017.170-175).
- 93 M. D. Teli and J. Sheikh, Extraction of chitosan from shrimp shells waste and application in antibacterial finishing of bamboo rayon, *Int. J. Biol. Macromol.*, 2012, **50**(5), 1195–1200, DOI: [10.1016/j.ijbiomac.2012.04.003](https://doi.org/10.1016/j.ijbiomac.2012.04.003).
- 94 A. Tarafdar and G. Biswas, Extraction of Chitosan from Prawn Shell Wastes and Examination of its Viable Commercial Applications, *International Journal on Theoretical and Applied Research in Mechanical Engineering*, 2013, **2**(3), 2319–3181.
- 95 A. Kucukgulmez, M. Celik, Y. Yanar, D. Sen, H. Polat and A. E. Kadak, Physicochemical characterization of chitosan extracted from *Metapenaeus stebbingi* shells, *Food Chem.*, 2011, **126**(3), 1144–1148, DOI: [10.1016/j.foodchem.2010.11.148](https://doi.org/10.1016/j.foodchem.2010.11.148).
- 96 Y. S. Puvvada, S. Vankayalapati and S. Sukhvasi, Extraction of chitin from chitosan from exoskeleton of shrimp for application in the pharmaceutical industry, *Int. Curr. Pharm. J.*, 2012, **1**(9), 258–263, DOI: [10.3329/icpj.v1i9.11616](https://doi.org/10.3329/icpj.v1i9.11616).
- 97 E. S. Abdou, K. S. A. Nagy and M. Z. Elsabee, Extraction and characterization of chitin and chitosan from local sources, *Bioresour. Technol.*, 2008, **99**(5), 1359–1367, DOI: [10.1016/j.biortech.2007.01.051](https://doi.org/10.1016/j.biortech.2007.01.051).
- 98 Y.-L. Huang and Y.-H. Tsai, Extraction of chitosan from squid pen waste by high hydrostatic pressure: Effects on physicochemical properties and antioxidant activities of chitosan, *Int. J. Biol. Macromol.*, 2020, **160**, 677–687, DOI: [10.1016/j.ijbiomac.2020.05.252](https://doi.org/10.1016/j.ijbiomac.2020.05.252).
- 99 F. A. A. Sagheer, M. A. Al-Sughayer, S. Muslim and M. Z. Elsabee, Extraction and characterization of chitin and chitosan from marine sources in Arabian Gulf, *Carbohydr. Polym.*, 2009, **77**(2), 410–419, DOI: [10.1016/j.carbpol.2009.01.032](https://doi.org/10.1016/j.carbpol.2009.01.032).
- 100 S. Kumari, P. Rath, A. Sri Hari Kumar and T. N. Tiwari, Extraction and characterization of chitin and chitosan from fishery waste by chemical method, *Environ. Technol. Innovation*, 2015, **3**, 77–85, DOI: [10.1016/j.eti.2015.01.002](https://doi.org/10.1016/j.eti.2015.01.002).
- 101 M. H. Mohammed, P. A. Williams and O. Tverezovskaya, Extraction of chitin from prawn shells and conversion to low molecular mass chitosan, *Food Hydrocolloids*, 2013, **31**(2), 166–171, DOI: [10.1016/j.foodhyd.2012.10.021](https://doi.org/10.1016/j.foodhyd.2012.10.021).
- 102 A. Abdulkarim, M. T. Isa, S. Abdulsalam, A. J. Muhammad and A. O. Ameh, Extraction and Characterisation of Chitin and Chitosan from Mussel Shell, *Civ. Environ. Res.*, 2013, **3**(2), 108–114.
- 103 G. Huet, *et al.*, Straightforward extraction and selective bioconversion of high purity chitin from *Bombyx eri* larva: Toward an integrated insect biorefinery, *Carbohydr. Polym.*, 2020, **228**, 115382, DOI: [10.1016/j.carbpol.2019.115382](https://doi.org/10.1016/j.carbpol.2019.115382).
- 104 M. Kaya, T. Baran, S. Erdoğan, A. Menteş, M. Aşan Özüsaglam and Y. S. Çakmak, Physicochemical comparison of chitin and chitosan obtained from larvae and adult Colorado potato beetle (*Leptinotarsa decemlineata*), *Mater. Sci. Eng., C*, 2014, **45**, 72–81, DOI: [10.1016/j.msec.2014.09.004](https://doi.org/10.1016/j.msec.2014.09.004).
- 105 K.-S. Chae, C.-S. Shin and W.-S. Shin, Characteristics of cricket (*Gryllus bimaculatus*) chitosan and chitosan-based nanoparticles, *Food Sci. Biotechnol.*, 2018, **27**(3), 631–639, DOI: [10.1007/s10068-018-0314-4](https://doi.org/10.1007/s10068-018-0314-4).
- 106 S. Erdogan and M. Kaya, High similarity in physicochemical properties of chitin and chitosan from nymphs and adults of a grasshopper, *Int. J. Biol. Macromol.*, 2016, **89**, 118–126, DOI: [10.1016/j.ijbiomac.2016.04.059](https://doi.org/10.1016/j.ijbiomac.2016.04.059).
- 107 E. B. Ibitoye, I. H. Lokman, M. N. M. Hezme, Y. M. Goh, A. B. Z. Zuki and A. A. Jimoh, Extraction and physicochemical characterization of chitin and chitosan isolated from house cricket, *Biomed. Mater.*, 2018, **13**(2), 025009, DOI: [10.1088/1748-605X/aa9dde](https://doi.org/10.1088/1748-605X/aa9dde).
- 108 Z. Draczynski, Honeybee corpses as an available source of chitin, *J. Appl. Polym. Sci.*, 2008, **109**(3), 1974–1981, DOI: [10.1002/app.28356](https://doi.org/10.1002/app.28356).
- 109 T. Hahn, A. Roth, R. Ji, E. Schmitt and S. Zibek, Chitosan production with larval exoskeletons derived from the insect protein production, *J. Biotechnol.*, 2020, **310**, 62–67, DOI: [10.1016/j.jbiotec.2019.12.015](https://doi.org/10.1016/j.jbiotec.2019.12.015).
- 110 M. Kaya, T. Baran, A. Mentes, M. Asaroglu, G. Sezen and K. O. Tozak, Extraction and Characterization of α -Chitin and Chitosan from Six Different Aquatic Invertebrates, *Food Biophys.*, 2014, **9**(2), 145–157, DOI: [10.1007/s11483-013-9327-y](https://doi.org/10.1007/s11483-013-9327-y).
- 111 M. Kaya, *et al.*, Differentiations of Chitin Content and Surface Morphologies of Chitins Extracted from Male and Female Grasshopper Species, *PLoS One*, 2015, **10**(1), e0115531, DOI: [10.1371/journal.pone.0115531](https://doi.org/10.1371/journal.pone.0115531).
- 112 M. Kaya, *et al.*, Comparison of physicochemical properties of chitins isolated from an insect (*Melolontha melolontha*)



- and a crustacean species (*Oniscus asellus*), *Zoomorphology*, 2014, **133**(3), 285–293, DOI: [10.1007/s00435-014-0227-6](https://doi.org/10.1007/s00435-014-0227-6).
- 113 M. Kaya, N. Bağrıaçık, O. Seyyar and T. Baran, Comparison of chitin structures derived from three common wasp species (*Vespa crabro* LINNAEUS, 1758, *Vespa orientalis* LINNAEUS, 1771 and *Vespula germanica* (FABRICIUS, 1793)), *Arch. Insect Biochem. Physiol.*, 2015, **89**(4), 204–217, DOI: [10.1002/arch.21237](https://doi.org/10.1002/arch.21237).
- 114 M. Kaya, B. Bitim, M. Mujtaba and T. Koyuncu, Surface morphology of chitin highly related with the isolated body part of butterfly (*Argynnis pandora*), *Int. J. Biol. Macromol.*, 2015, **81**, 443–449, DOI: [10.1016/j.ijbiomac.2015.08.021](https://doi.org/10.1016/j.ijbiomac.2015.08.021).
- 115 A. Khayrova, S. Lopatin and V. Varlamov, Black Soldier Fly *Hermetia illucens* as a Novel Source of Chitin and Chitosan, *Int. J. Sci.*, 2019, **8**(04), 81–86, DOI: [10.18483/ijSci.2015](https://doi.org/10.18483/ijSci.2015).
- 116 M. Kaya, *et al.*, Conversion of Waste Parasitic Insect (*Hylobius abietis* L.) into Antioxidative, Antimicrobial and Biodegradable Films, *J. Renewable Mater.*, 2019, **7**(3), 215–226, DOI: [10.32604/jrm.2019.00002](https://doi.org/10.32604/jrm.2019.00002).
- 117 M. Kaya, B. Akyuz, E. Bulut, I. Sargin, F. Eroglu and G. Tan, Chitosan nanofiber production from *Drosophila* by electrospinning, *Int. J. Biol. Macromol.*, 2016, **92**, 49–55, DOI: [10.1016/j.ijbiomac.2016.07.021](https://doi.org/10.1016/j.ijbiomac.2016.07.021).
- 118 M. Kaya, *et al.*, Extraction and characterization of chitin and chitosan with antimicrobial and antioxidant activities from cosmopolitan Orthoptera species (Insecta), *Biotechnol. Bioprocess Eng.*, 2015, **20**(1), 168–179, DOI: [10.1007/s12257-014-0391-z](https://doi.org/10.1007/s12257-014-0391-z).
- 119 M. Kaya, *et al.*, Gender influences differentiation of chitin among body parts, *Arch. Insect Biochem. Physiol.*, 2016, **93**(2), 96–109, DOI: [10.1002/arch.21344](https://doi.org/10.1002/arch.21344).
- 120 M. Kim, *et al.*, Extraction of chitin and chitosan from housefly, *Musca domestica* , pupa shells, *Entomol. Res.*, 2016, **46**(5), 324–328, DOI: [10.1111/1748-5967.12175](https://doi.org/10.1111/1748-5967.12175).
- 121 J. Ma, C. Xin and C. Tan, Preparation, physicochemical and pharmaceutical characterization of chitosan from *Catharsius molossus* residue, *Int. J. Biol. Macromol.*, 2015, **80**, 547–556, DOI: [10.1016/j.ijbiomac.2015.07.027](https://doi.org/10.1016/j.ijbiomac.2015.07.027).
- 122 N. H. Marei, E. A. El-Samie, T. Salah, G. R. Saad and A. H. M. Elwahy, Isolation and characterization of chitosan from different local insects in Egypt, *Int. J. Biol. Macromol.*, 2016, **82**, 871–877, DOI: [10.1016/j.ijbiomac.2015.10.024](https://doi.org/10.1016/j.ijbiomac.2015.10.024).
- 123 J. G. Monter-Miranda, *et al.*, Extraction and characterization of physicochemical morphological, and structural properties of chitin and chitosan from *Brachystola magna* (Girard), *Rev. Mex. Ing. Quim.*, 2016, **15**(3), 749–761, DOI: [10.24275/rmiq/Bio1028](https://doi.org/10.24275/rmiq/Bio1028).
- 124 M. Zhang, A. Haga, H. Sekiguchi and S. Hirano, Structure of insect chitin isolated from beetle larva cuticle and silkworm (*Bombyx mori*) pupa exuvia, *Int. J. Biol. Macromol.*, 2000, **27**(1), 99–105, DOI: [10.1016/S0141-8130\(99\)00123-3](https://doi.org/10.1016/S0141-8130(99)00123-3).
- 125 A.-J. Zhang, *et al.*, Preparation and characterisation of food grade chitosan from housefly larvae, *Czech J. Food Sci.*, 2011, **29**(6), 616–623, DOI: [10.17221/100/2010-CJFS](https://doi.org/10.17221/100/2010-CJFS).
- 126 S. V. Nemtsev, O. Yu. Zueva, M. R. Khismatullin, A. I. Albulov and V. P. Varlamov, Isolation of Chitin and Chitosan from Honeybees, *Appl. Biochem. Microbiol.*, 2004, **40**(1), 39–43, DOI: [10.1023/B:ABIM.0000010349.62620.49](https://doi.org/10.1023/B:ABIM.0000010349.62620.49).
- 127 S.-J. Wu, S.-K. Pan, H.-B. Wang and J.-H. Wu, Preparation of chitoooligosaccharides from cicada slough and their antibacterial activity, *Int. J. Biol. Macromol.*, 2013, **62**, 348–351, DOI: [10.1016/j.ijbiomac.2013.09.042](https://doi.org/10.1016/j.ijbiomac.2013.09.042).
- 128 P. M. Oduor, M. H. Struszczyk and M. G. Peter, Characterisation of chitosan from blowfly larvae and some crustacean species from Kenyan marine waters prepared under different conditions, *Discovery Innovation*, 2008, **20**(2), 129–136.
- 129 A. T. Paulino, J. I. Simionato, J. C. Garcia and J. Nozaki, Characterization of chitosan and chitin produced from silkworm crysalides, *Carbohydr. Polym.*, 2006, **64**(1), 98–103, DOI: [10.1016/j.carbpol.2005.10.032](https://doi.org/10.1016/j.carbpol.2005.10.032).
- 130 A. Waško, P. Bulak, M. Polak-Berecka, K. Nowak, C. Polakowski and A. Bieganski, The first report of the physicochemical structure of chitin isolated from *Hermetia illucens*, *Int. J. Biol. Macromol.*, 2016, **92**, 316–320, DOI: [10.1016/j.ijbiomac.2016.07.038](https://doi.org/10.1016/j.ijbiomac.2016.07.038).
- 131 C.-S. Shin, D.-Y. Kim and W.-S. Shin, Characterization of chitosan extracted from Mealworm Beetle (*Tenebrio molitor*, *Zophobas morio*) and Rhinoceros Beetle (*Allomyrina dichotoma*) and their antibacterial activities, *Int. J. Biol. Macromol.*, 2019, **125**, 72–77, DOI: [10.1016/j.ijbiomac.2018.11.242](https://doi.org/10.1016/j.ijbiomac.2018.11.242).
- 132 G. Tan, M. Kaya, A. Tevlek, I. Sargin and T. Baran, Antitumor activity of chitosan from mayfly with comparison to commercially available low, medium and high molecular weight chitosans, *In Vitro Cell. Dev. Biol.: Anim.*, 2018, **54**(5), 366–374, DOI: [10.1007/s11626-018-0244-8](https://doi.org/10.1007/s11626-018-0244-8).
- 133 C. Song, H. Yu, M. Zhang, Y. Yang and G. Zhang, Physicochemical properties and antioxidant activity of chitosan from the blowfly *Chrysomya megacephala* larvae, *Int. J. Biol. Macromol.*, 2013, **60**, 347–354, DOI: [10.1016/j.ijbiomac.2013.05.039](https://doi.org/10.1016/j.ijbiomac.2013.05.039).
- 134 C. Y. Soon, Y. B. Tee, C. H. Tan, A. T. Rosnita and A. Khalina, Extraction and physicochemical characterization of chitin and chitosan from *Zophobas morio* larvae in varying sodium hydroxide concentration, *Int. J. Biol. Macromol.*, 2018, **108**, 135–142, DOI: [10.1016/j.ijbiomac.2017.11.138](https://doi.org/10.1016/j.ijbiomac.2017.11.138).
- 135 T. Wu, S. Zivanovic, F. A. Draughon and C. E. Sams, Chitin and Chitosan Value-Added Products from Mushroom Waste, *J. Agric. Food Chem.*, 2004, **52**(26), 7905–7910, DOI: [10.1021/jf0492565](https://doi.org/10.1021/jf0492565).
- 136 E. Poverenov, *et al.*, Potential of chitosan from mushroom waste to enhance quality and storability of fresh-cut melons, *Food Chem.*, 2018, **268**, 233–241, DOI: [10.1016/j.foodchem.2018.06.045](https://doi.org/10.1016/j.foodchem.2018.06.045).
- 137 I. Irbe, L. Andze, M. Blumfelde, A. Verovkins, I. Filipova and J. Zoldners, Harvesting of Mycelial Biomass of Selected Basidiomycetes for Extraction of Chitosan, *Polymers*, 2023, **15**(17), 3548.



- 138 M. Ugochukwu, I. Okwulehie and K. Egbucha, Chitosan production of *Pleurotus ostreatus* (Jacq. ex fr.) p. kumm cultivated on different substrates, *Int. J. Mod. Appl. Sci. Res.*, 2022, **26**, 5–22.
- 139 Z. Ban, *et al.*, Efficient production of fungal chitosan utilizing an advanced freeze-thawing method; quality and activity studies, *Food Hydrocolloids*, 2018, **81**, 380–388, DOI: [10.1016/j.foodhyd.2018.03.010](https://doi.org/10.1016/j.foodhyd.2018.03.010).
- 140 A. Hassainia, H. Satha and S. Boufi, Chitin from *Agaricus bisporus*: Extraction and characterization, *Int. J. Biol. Macromol.*, 2018, **117**, 1334–1342, DOI: [10.1016/j.ijbiomac.2017.11.172](https://doi.org/10.1016/j.ijbiomac.2017.11.172).
- 141 M. Kannan, M. Nesakumari and K. Rajarathinam, Production and Characterization of Mushroom Chitosan under Solid-St, *Adv. Biol. Res.*, 2010, **4**(1), 10–13.
- 142 M. M. Benamar, N. Ammar-Khodja and L. Adour, Biopolymers isolation (chitin and chitosan) from mushroom biomass of *Pleurotus ostreatus* (Jacq: Fries) Kummer, *Alger. J. Environ. Sci. Technol.*, 2022, **8**(3), 2611–2617.
- 143 Y. Boureghda, H. Satha and F. Bendebane, Chitin–Glucan Complex from *Pleurotus ostreatus* Mushroom: Physicochemical Characterization and Comparison of Extraction Methods, *Waste Biomass Valorization*, 2021, **12**(11), 6139–6153, DOI: [10.1007/s12649-021-01449-3](https://doi.org/10.1007/s12649-021-01449-3).
- 144 F. Di Mario, P. Rapanà, U. Tomati and E. Galli, Chitin and chitosan from Basidiomycetes, *Int. J. Biol. Macromol.*, 2008, **43**(1), 8–12, DOI: [10.1016/j.ijbiomac.2007.10.005](https://doi.org/10.1016/j.ijbiomac.2007.10.005).
- 145 N. K. Kalutharage and D. L. Rathnasinghe, A study of chitosan and glucosamine isolated from Sri Lankan local mushroom *Schizophyllum commune* and oyster mushroom (*Pleurotus ostreatus*), *Mater. Today Proc.*, 2020, **23**, 119–122, DOI: [10.1016/j.matpr.2019.07.713](https://doi.org/10.1016/j.matpr.2019.07.713).
- 146 J. Johny, K. Egappan and R. R. Ragnathan, Microbial Extraction Of Chitin And Chitosan From *Pleurotus* Spp, Its Characterization And Antimicrobial Activity, *Int. J. Curr. Pharm. Res.*, 2016, **9**(1), 88, DOI: [10.22159/ijcpr.2017v9i1.16623](https://doi.org/10.22159/ijcpr.2017v9i1.16623).
- 147 S. P. Ospina Álvarez, *et al.*, Comparison of Extraction Methods of Chitin from *Ganoderma lucidum* Mushroom Obtained in Submerged Culture, *BioMed Res. Int.*, 2014, **2014**, 1–7, DOI: [10.1155/2014/169071](https://doi.org/10.1155/2014/169071).
- 148 S. O. Majekodunmi, E. O. Olorunsola, U. C. Ofiwe, A. S. Udobre and E. Akpan, Material properties of chitosan from shells of *Egeria radiata*: Drug delivery considerations, *J. Coastal Life Med.*, 2017, **5**(7), 321–324, DOI: [10.12980/jclm.5.2017J7-2](https://doi.org/10.12980/jclm.5.2017J7-2).
- 149 A. I. Zamri, N. F. Latiff, Q. H. Abdullah and F. Ahmad, Extraction and optimization of chitosan from razor clam (*Ensis arcuatus*) shells by using response surface methodology (RSM), *Food Res.*, 2020, **4**(3), 674–678, DOI: [10.26656/fr.2017.4\(3\).308](https://doi.org/10.26656/fr.2017.4(3).308).
- 150 R. Varma and S. Vasudevan, Extraction, Characterization, and Antimicrobial Activity of Chitosan from Horse Mussel *Modiolus modiolus*, *ACS Omega*, 2020, **5**(32), 20224–20230, DOI: [10.1021/acsomega.0c01903](https://doi.org/10.1021/acsomega.0c01903).
- 151 S. O. Majekodunmi, E. O. Olorunsola and C. C. Uzoaganobi, Comparative Physicochemical Characterization of Chitosan from Shells of Two Bivalved Mollusks from Two Different Continents, *Am. J. Polym. Sci.*, 2017, **7**(1), 15–22.
- 152 L. Handayani, F. Syahputra and Y. Astuti, Utilization and Characterization of Oyster Shell as Chitosan and Nanochitosan, *J. Kim. Sains Apl.*, 2018, **21**(4), 224–231, DOI: [10.14710/jksa.21.4.224-231](https://doi.org/10.14710/jksa.21.4.224-231).
- 153 H. Rasti, K. Parivar, J. Baharara, M. Iranshahi and F. Namvar, Chitin from the mollusc chiton: extraction, characterization and chitosan preparation, *Iran. J. Pharm. Res.*, 2017, **16**(1), 366.
- 154 E. Alabaraoye, M. Achilonu and R. Hester, Biopolymer (Chitin) from Various Marine Seashell Wastes: Isolation and Characterization, *J. Polym. Environ.*, 2018, **26**(6), 2207–2218, DOI: [10.1007/s10924-017-1118-y](https://doi.org/10.1007/s10924-017-1118-y).
- 155 F. Zentz, L. Bédouet, M. J. Almeida, C. Milet, E. Lopez and M. Giraud, Characterization and Quantification of Chitosan Extracted from Nacre of the Abalone *Haliotis tuberculata* and the Oyster *Pinctada maxima*, *Mar. Biotechnol.*, 2001, **3**(1), 36–44, DOI: [10.1007/s101260000042](https://doi.org/10.1007/s101260000042).
- 156 N. E. N. Sugijanto, S. Kartosentono, P. T. Hardani, N. E. N. Sugijanto and S. Kartosentono, Heavy metals bioremediation by shells dust and chitosan derived from *Bellamyia javanica* Snail, an Eco-friendly biosorbent, *Res. J. Pharm. Technol.*, 2021, **14**(3), 1555–1560.
- 157 A. Shanmugam, K. Kathiresan and L. Nayak, Preparation, characterization and antibacterial activity of chitosan and phosphorylated chitosan from cuttlebone of *Sepia kubiensis* (Hoyle, 1885), *Biotechnol. Rep.*, 2016, **9**, 25–30, DOI: [10.1016/j.btre.2015.10.007](https://doi.org/10.1016/j.btre.2015.10.007).
- 158 A. Anoop, T. Gobinath and S. Ravichandran, Physicochemical properties and structural characterization of chitosan synthesized from rare spined murex, *Murex trapa* (Roding, 1798) shell waste, *Res. J. Pharm. Technol.*, 2022, **15**(12), 5729–5735, DOI: [10.52711/0974-360X.2022.00966](https://doi.org/10.52711/0974-360X.2022.00966).
- 159 S. H. Zainal, N. H. Mohd, N. Suhaili, F. H. Anuar, A. M. Lazim and R. Othaman, Preparation of cellulose-based hydrogel: a review, *J. Mater. Res. Technol.*, 2021, **10**, 935–952, DOI: [10.1016/j.jmrt.2020.12.012](https://doi.org/10.1016/j.jmrt.2020.12.012).
- 160 K. Mohan, *et al.*, Extraction and characterization of chitin from sea snail *Conus inscriptus* (Reeve, 1843), *Int. J. Biol. Macromol.*, 2019, **126**, 555–560, DOI: [10.1016/j.ijbiomac.2018.12.241](https://doi.org/10.1016/j.ijbiomac.2018.12.241).
- 161 A. A. Abideen, T. A. Uthman, S. A. Adeniyi, K. A. Lawal and O. E. Oluwadare, Production and characterisation of chitosan from chitin of snail shells by sequential modification process, *Afr. J. Biotechnol.*, 2023, **22**(2), 39–53, DOI: [10.5897/AJB2020.17135](https://doi.org/10.5897/AJB2020.17135).
- 162 Y. C. Danarto and S. Distantina, Optimizing deacetylation process for chitosan production from green mussel (*perna viridis*) shell, presented at the *Proceedings of International Seminar on Mathematics, Science, and Computer Science Education (MSCEIS 2015)*, Bandung, Indonesia, 2016, p. 030028, DOI: [10.1063/1.4941494](https://doi.org/10.1063/1.4941494).
- 163 E. Siswoyo, R. N. Zahra, N. H. A. Mai, A. Nurmiyanto, K. Umamura and T. Boving, Chitosan of blood cockle shell (*Anadara granosa*) as a natural coagulant for



- removal of total suspended solids (TSS) and turbidity of well-water, *Egypt. J. Aquat. Res.*, 2023, **49**(3), 283–289, DOI: [10.1016/j.ejar.2023.04.004](https://doi.org/10.1016/j.ejar.2023.04.004).
- 164 V. Aylanc, *et al.*, Natural β -chitin-protein complex film obtained from waste razor shells for transdermal capsaicin carrier, *Int. J. Biol. Macromol.*, 2020, **155**, 508–515, DOI: [10.1016/j.ijbiomac.2020.03.232](https://doi.org/10.1016/j.ijbiomac.2020.03.232).
- 165 E. H. Abed, N. I. A. Ameen and L. A. Jazaa, Extraction of Chitosan from Kentish Snail Exoskeleton Shell's, *Monacha cantiana* (Montagu, 1803) for the Pharmaceutical Application, *J. Int. Environ. Appl. Sci.*, 2017, **12**, 125–130.
- 166 J. R. Cadano, *et al.*, A comparative study on the raw chitin and chitosan yields of common bio-waste from Philippine seafood, *Environ. Sci. Pollut. Res.*, 2021, **28**(10), 11954–11961, DOI: [10.1007/s11356-020-08380-5](https://doi.org/10.1007/s11356-020-08380-5).
- 167 S. Kaewboonruang, N. Phatrabuddha, P. Sawangwong and S. Pitaksanurat, Comparative studies on the extraction of chitin-chitosan from golden apple snail shells at the control field, PhD dissertation, Burapha Univ., 2016.
- 168 T. Gobinath, S. Thamizhselvan, A. Ramakrishnan and S. Ravichandran, Preparation and Characterization of Chitosan from *Perna viridis* (Linnaeus, 1758) shell waste as raw material, *Res. J. Pharm. Technol.*, 2021, **14**(5), 2757–2762, DOI: [10.52711/0974-360X.2021.00486](https://doi.org/10.52711/0974-360X.2021.00486).
- 169 R. Thangaraj Jebarani, S. Muthukumarasamy and M. Theivasigamani, Physicochemical and functional characterization of chitosan from horn snail gastropod *Telescopium telescopium*, *J. Appl. Pharm. Sci.*, 2021, **11**, 052–058, DOI: [10.7324/JAPS.2021.110207](https://doi.org/10.7324/JAPS.2021.110207).
- 170 N. W. Sangwaranatee, K. Teanchai, S. Kongsriprapan and W. Siriprom, Characterization and analyzation of chitosan powder from *Perna Viridis* shell, *Mater. Today Proc.*, 2018, **5**(6), 13922–13925, DOI: [10.1016/j.matpr.2018.02.041](https://doi.org/10.1016/j.matpr.2018.02.041).
- 171 P. Ramasamy, *et al.*, Characterization of bioactive chitosan and sulfated chitosan from *Doryteuthis singhalensis* (Ortmann, 1891), *Int. J. Biol. Macromol.*, 2017, **99**, 682–691, DOI: [10.1016/j.ijbiomac.2017.03.041](https://doi.org/10.1016/j.ijbiomac.2017.03.041).
- 172 N. Rokhati, T. Istirokhatun, D. T. Apriyanti and H. Susanto, Production of Chitosan from *Amusium sp* Scallop Shell Waste, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2017, **55**, 012071, DOI: [10.1088/1755-1315/55/1/012071](https://doi.org/10.1088/1755-1315/55/1/012071).
- 173 A. Barwin Vino, P. Ramasamy, S. Vairamani and A. Shanmugam, Physicochemical characterization of biopolymers chitin and chitosan extracted from squid *Doryteuthis sibogae* adam, 1954 pen, *Int. J. Pharm. Res. Dev.*, 2011, **2**(12), 181–190.
- 174 P. Ramasamy, N. Subhapradha, V. Shanmugam and A. Shanmugam, Extraction, characterization and antioxidant property of chitosan from cuttlebone *Sepia kobeensis* (Hoyle 1885), *Int. J. Biol. Macromol.*, 2014, **64**, 202–212.
- 175 L. L. Reys, *et al.*, Revealing the potential of squid chitosan-based structures for biomedical applications, *Biomed. Mater.*, 2013, **8**(4), 045002, DOI: [10.1088/1748-6041/8/4/045002](https://doi.org/10.1088/1748-6041/8/4/045002).
- 176 S. Hajji, *et al.*, Structural differences between chitin and chitosan extracted from three different marine sources, *Int. J. Biol. Macromol.*, 2014, **65**, 298–306, DOI: [10.1016/j.ijbiomac.2014.01.045](https://doi.org/10.1016/j.ijbiomac.2014.01.045).
- 177 J. Huang, *et al.*, Effect of quaternization degree on physicochemical and biological activities of chitosan from squid pens, *Int. J. Biol. Macromol.*, 2014, **70**, 545–550, DOI: [10.1016/j.ijbiomac.2014.07.017](https://doi.org/10.1016/j.ijbiomac.2014.07.017).
- 178 T. Sathasivam, *et al.*, Transforming textile waste into nanocellulose for a circular future, *Nanoscale*, 2024, **16**(30), 14168–14194, DOI: [10.1039/D4NR01839G](https://doi.org/10.1039/D4NR01839G).
- 179 N. C. Huey, Extraction, isolation, characterization and applications of cellulose derived from orange peel, PhD Diss., UTAR, 2019.
- 180 K. Ketheeswaran, S. Shetranjiwalla, M. Krishnapillai and L. Galagedara, Incorporating biochar to make hydrogel composites with improved structural properties, valorized from waste-paper mill sludge and forestry residues using energy efficient protocols, *RSC Sustainability*, 2024, **2**(11), 3478–3489.
- 181 G. Joshi, S. Naithani, V. K. Varshney, S. S. Bisht, V. Rana and P. K. Gupta, Synthesis and characterization of carboxymethyl cellulose from office waste paper: A greener approach towards waste management, *Waste Manage.*, 2015, **38**, 33–40, DOI: [10.1016/j.wasman.2014.11.015](https://doi.org/10.1016/j.wasman.2014.11.015).
- 182 C. Campano, R. Miranda, N. Merayo, C. Negro and A. Blanco, Direct production of cellulose nanocrystals from old newspapers and recycled newsprint, *Carbohydr. Polym.*, 2017, **173**, 489–496, DOI: [10.1016/j.carbpol.2017.05.073](https://doi.org/10.1016/j.carbpol.2017.05.073).
- 183 G. Joshi, V. Rana, S. Naithani, V. K. Varshney, A. Sharma and J. S. Rawat, Chemical modification of waste paper: An optimization towards hydroxypropyl cellulose synthesis, *Carbohydr. Polym.*, 2019, **223**, 115082, DOI: [10.1016/j.carbpol.2019.115082](https://doi.org/10.1016/j.carbpol.2019.115082).
- 184 W. Wongvitvichot, S. Pithakratanayothin, S. Wongkasemjit and T. Chaisuwan, Fast and practical synthesis of carboxymethyl cellulose from office paper waste by ultrasonic-assisted technique at ambient temperature, *Polym. Degrad. Stab.*, 2021, **184**, 109473, DOI: [10.1016/j.polymdegradstab.2020.109473](https://doi.org/10.1016/j.polymdegradstab.2020.109473).
- 185 W. Lei, *et al.*, Cellulose nanocrystals obtained from office waste paper and their potential application in PET packing materials, *Carbohydr. Polym.*, 2018, **181**, 376–385, DOI: [10.1016/j.carbpol.2017.10.059](https://doi.org/10.1016/j.carbpol.2017.10.059).
- 186 H. Wang, D. Li and R. Zhang, Preparation of Ultralong Cellulose Nanofibers and Optically Transparent Nanopapers Derived from Waste Corrugated Paper Pulp, *BioResources*, 2013, **8**(1), 1374–1384, DOI: [10.15376/biores.8.1.1374-1384](https://doi.org/10.15376/biores.8.1.1374-1384).
- 187 D.-T. Van-Pham, T. Y. N. Pham, M. C. Tran, C.-N. Nguyen and Q. Tran-Cong-Miyata, Extraction of thermally stable cellulose nanocrystals in short processing time from waste newspaper by conventional acid hydrolysis, *Mater. Res. Express*, 2020, **7**(6), 065004, DOI: [10.1088/2053-1591/ab9668](https://doi.org/10.1088/2053-1591/ab9668).
- 188 R. R. Casillas, K. F. B. Rodríguez, R. H. Cruz-Estrada, F. Dávalos-Olivares, F. Navarro-Arzate and



- K. G. Satyanarayana, Isolation and Characterization of Cellulose Nanocrystals Created from Recycled Laser Printed Paper, *BioResources*, 2018, 13(4), 7404–7429, DOI: [10.15376/biores.13.4.7404-7429](https://doi.org/10.15376/biores.13.4.7404-7429).
- 189 S. Thambiraj and D. Ravi Shankaran, Preparation and physicochemical characterization of cellulose nanocrystals from industrial waste cotton, *Appl. Surf. Sci.*, 2017, 412, 405–416, DOI: [10.1016/j.apsusc.2017.03.272](https://doi.org/10.1016/j.apsusc.2017.03.272).
- 190 M.-X. Ruiz-Caldas, *et al.*, Citrated cellulose nanocrystals from post-consumer cotton textiles, *J. Mater. Chem. A*, 2023, 11(13), 6854–6868, DOI: [10.1039/D2TA09456H](https://doi.org/10.1039/D2TA09456H).
- 191 S. Huang, R. Tao, A. Ismail and Y. Wang, Cellulose Nanocrystals Derived from Textile Waste through Acid Hydrolysis and Oxidation as Reinforcing Agent of Soy Protein Film, *Polymers*, 2020, 12(4), 958, DOI: [10.3390/polym12040958](https://doi.org/10.3390/polym12040958).
- 192 R. Xiong, X. Zhang, D. Tian, Z. Zhou and C. Lu, Comparing microcrystalline with spherical nanocrystalline cellulose from waste cotton fabrics, *Cellulose*, 2012, 19(4), 1189–1198, DOI: [10.1007/s10570-012-9730-4](https://doi.org/10.1007/s10570-012-9730-4).
- 193 Y. Yue, *et al.*, Comparative properties of cellulose nanocrystals from native and mercerized cotton fibers, *Cellulose*, 2012, 19(4), 1173–1187, DOI: [10.1007/s10570-012-9714-4](https://doi.org/10.1007/s10570-012-9714-4).
- 194 Z. Wang, Z. Yao, J. Zhou and Y. Zhang, Reuse of waste cotton cloth for the extraction of cellulose nanocrystals, *Carbohydr. Polym.*, 2017, 157, 945–952, DOI: [10.1016/j.carbpol.2016.10.044](https://doi.org/10.1016/j.carbpol.2016.10.044).
- 195 J. M. R. Jayasinghe, A. M. P. B. Samarasekara, and D. A. S. Amarasinghe, Synthesis and Characterization of Microcrystalline Cellulose from Cotton Textile Waste, in *2020 Moratuwa Engineering Research Conference (MERCon)*, IEEE, Moratuwa, Sri Lanka, 2020, pp. 187–192, DOI: [10.1109/MERCon50084.2020.9185346](https://doi.org/10.1109/MERCon50084.2020.9185346).
- 196 P. Shahbazi, T. Behzad and P. Heidarian, Isolation of cellulose nanofibers from poplar wood and wheat straw: optimization of bleaching step parameters in a chemo-mechanical process by experimental design, *Wood Sci. Technol.*, 2017, 51(5), 1173–1187, DOI: [10.1007/s00226-017-0929-2](https://doi.org/10.1007/s00226-017-0929-2).
- 197 M. Benali, A. Oulmekki and J. Toyir, The Impact of the Alkali-Bleaching Treatment on the Isolation of Natural Cellulosic Fibers from *Juncus Effesus* L Plant, *Fibers Polym.*, 2024, 25(2), 525–533, DOI: [10.1007/s12221-023-00441-z](https://doi.org/10.1007/s12221-023-00441-z).
- 198 S. Vinhas, M. Sarraguça, T. Moniz, S. Reis and M. Rangel, A New Microwave-Assisted Protocol for Cellulose Extraction from Eucalyptus and Pine Tree Wood Waste, *Polymers*, 2023, 16(1), 20, DOI: [10.3390/polym16010020](https://doi.org/10.3390/polym16010020).
- 199 A. Kumar, Y. Singh Negi, V. Choudhary and N. Kant Bhardwaj, Characterization of Cellulose Nanocrystals Produced by Acid-Hydrolysis from Sugarcane Bagasse as Agro-Waste, *J. Mater. Phys. Chem.*, 2020, 2(1), 1–8, DOI: [10.12691/jmpc-2-1-1](https://doi.org/10.12691/jmpc-2-1-1).
- 200 B. M. Cherian, A. L. Leão, S. F. De Souza, S. Thomas, L. A. Pothan and M. Kottaisamy, Isolation of nanocellulose from pineapple leaf fibres by steam explosion, *Carbohydr. Polym.*, 2010, 81(3), 720–725, DOI: [10.1016/j.carbpol.2010.03.046](https://doi.org/10.1016/j.carbpol.2010.03.046).
- 201 Md. S. Islam, N. Kao, S. N. Bhattacharya, and R. Gupta, An investigation between high and low pressure processes for nanocrystalline cellulose production from agro-waste biomass, presented at the *PROCEEDINGS of PPS-32: the 32nd International Conference of the Polymer Processing Society - Conference Papers*, Lyon, France, 2017, p. 070002, DOI: [10.1063/1.5016729](https://doi.org/10.1063/1.5016729).
- 202 F. Hemmati, S. M. Jafari, M. Kashaninejad and M. Barani Motlagh, Synthesis and characterization of cellulose nanocrystals derived from walnut shell agricultural residues, *Int. J. Biol. Macromol.*, 2018, 120, 1216–1224, DOI: [10.1016/j.ijbiomac.2018.09.012](https://doi.org/10.1016/j.ijbiomac.2018.09.012).
- 203 X.-F. Sun, R.-C. Sun, Y. Su and J.-X. Sun, Comparative study of crude and purified cellulose from wheat straw, *J. Agric. Food Chem.*, 2004, 52(4), 839–847.
- 204 Z. Wang, J. Li, J. P. Barford, K. Hellgratd and G. McKay, A comparison of chemical treatment methods for the preparation of rice husk cellulosic fibers, *Int. J. Environ. Agric. Res.*, 2016, 2, 2454–1850.
- 205 A. E. Karaca, C. Özel, A. C. Özarslan and S. Yücel, The simultaneous extraction of cellulose fiber and crystal biogenic silica from the same rice husk and evaluation in cellulose-based composite bioplastic films, *Polym. Compos.*, 2022, 43(10), 6838–6853, DOI: [10.1002/pc.26729](https://doi.org/10.1002/pc.26729).
- 206 E. Syafri, A. Kasim, H. Abrial and A. Asben, Cellulose nanofibers isolation and characterization from ramie using a chemical-ultrasonic treatment, *J. Nat. Fibers*, 2019, 11, 1145–1155.
- 207 M. F. Rosa, *et al.*, Cellulose nanowhiskers from coconut husk fibers: Effect of preparation conditions on their thermal and morphological behavior, *Carbohydr. Polym.*, 2010, 81(1), 83–92, DOI: [10.1016/j.carbpol.2010.01.059](https://doi.org/10.1016/j.carbpol.2010.01.059).
- 208 S. W. Gadzama, O. Sunmonu, U. Isiaku and A. Danladi, Isolation and characterization of nanocellulose from pineapple leaf fibres via chemo-mechanical method, *Sci. World J.*, 2020, 15(2), 100–105.
- 209 S. Jancy, R. Shruthy and R. Preetha, Fabrication of packaging film reinforced with cellulose nanoparticles synthesised from jack fruit non-edible part using response surface methodology, *Int. J. Biol. Macromol.*, 2020, 142, 63–72, DOI: [10.1016/j.ijbiomac.2019.09.066](https://doi.org/10.1016/j.ijbiomac.2019.09.066).
- 210 Y. Habibi, M. Mahrouz and M. R. Vignon, Microfibrillated cellulose from the peel of prickly pear fruits, *Food Chem.*, 2009, 115(2), 423–429, DOI: [10.1016/j.foodchem.2008.12.034](https://doi.org/10.1016/j.foodchem.2008.12.034).
- 211 F. J. Moscoso-Sánchez, A. Alvarad, L. Martínez-Chávez, R. Hernández-Montelongo, V. V. F. Escamilla and G. C. Escamilla, The effects of henequen cellulose treated with polyethylene glycol on properties of polylactic acid composites, *BioResources*, 2019, 14(2), 2707–2726, DOI: [10.15376/biores.14.2.2707-2726](https://doi.org/10.15376/biores.14.2.2707-2726).
- 212 G. Siqueira, K. Oksman, S. K. Tadokoro and A. P. Mathew, Re-dispersible carrot nanofibers with high mechanical properties and reinforcing capacity for use in composite materials, *Compos. Sci. Technol.*, 2016, 123, 49–56.

