## ChemComm



### COMMUNICATION

View Article Online



Cite this: Chem. Commun., 2023, **59**, 1781

Received 1st December 2022 Accepted 18th January 2023

DOI: 10.1039/d2cc06548q

rsc.li/chemcomm

# Circularly polarized near-infrared phosphorescence of chiral chromium(III) complexes†

Yang Cheng, Jiang He, Wenjie Zou, Xiaoyong Chang, Qingging Yang p \* and Wei Lu P\*

Homoleptic Cr(III) complexes containing anionic tridentate 1,8-(bisoxazolyl)carbazolide ligands are phosphorescent in deaerated solutions with peak maxima in the range of 813-845 nm. The ligand carbon-centred chirality has been transferred to the helical chirality of the complexes and hence induced circularly polarized NIRemissions with dissymmetry factor in the scale of 2.0  $\times$  10<sup>-3</sup>.

Circularly polarized luminescence (CPL) active materials have recently attracted considerable attention due to their potential applications, such as in stereoscopic displays, smart sensors/ probes, organic light-emitting diodes (OLEDs) and advanced security inks. In particular, extending and consolidating circularly polarized emission in the near infrared (NIR) region is highly desirable for versatile applicability of biological imaging or photonics.<sup>2</sup> However, the development of NIR-active chiroptical luminogens remains a considerable challenge when compared with the classical visible CPL emitters.  $^{1h,3}$  The emission in the NIR region is expected to yield lower quantum yield  $(\Phi)$  due to efficient non-radiative deactivation pathways, recognized as the 'energy gap law'. 4 So far, only a few studies with NIR-CPLs over 700 nm have been reported,3,5 thus portending the great challenges and tremendous prospects of the NIR-CPL emitters.

CPL emitters are generally evaluated by the luminescence dissymmetry factor  $(g_{lum})^{1a}$  and emission quantum yield  $(\Phi)$ . Due to the trade-off between these two parameters, materials with both large  $|g_{\text{lum}}|$  and  $\Phi$  values are still limited. Accordingly, the electronically dipole-forbidden and magnetically allowed transitions such as intrashell f-f and d-d are promising solutions to provide high  $g_{lum}$ . Recently, Cr(III) complexes that exhibit strong emission in the red to NIR region have been

Department of Chemistry, Southern University of Science and Technology, Shenzhen, Guangdong 518055, P. R. China. E-mail: yangqq3@sustech.edu.cn, luw@sustech.edu.cn

† Electronic supplementary information (ESI) available: characterization data and additional spectra, CCDC 2223181, 2223182 and 2223185. For ESI and crystallographic data in CIF or other electronic format see DOI: https://doi.org/ 10.1039/d2cc06548g

achieved by an introduction of strong-field ligands. Due to the d<sup>3</sup> electronic configuration and the strong ligand field environments, pseudo-octahedral Cr(III) complexes display magnetically-allowed but electric-dipole forbidden spin-flip  $Cr(^2E/^2T_1 \rightarrow {}^4A_2)$  emission, which makes them ideal candidates for NIR-CPL materials,7 alternative to precious metals (Ru, Ir, Pt, or Au)<sup>8</sup> and lanthanides. <sup>1b,9</sup> In this way, several attempts have been made recently. A recent example was the chiral resolution of  $[Cr(dqp)_2]^{3+}$  (dqp = 2,6di(quinolin-8-yl)pyridine), which achieved high glum of 0.2 at 749 nm.<sup>5</sup> Moreover, the functionalization of the dqp ligand with a methoxy group has been proven to improve the chiral resolution, provide high  $\Phi$  (17%) and maintain the high  $g_{\text{lum}}$ . <sup>5g</sup> The molecular ruby  $[Cr(ddpd)_2]^{3+}$  (ddpd = N,N'-dimethyl-N,N''-dimethyl-N,Ndipyridin-2-ylpyridine-2,6-diamine) can also be resolved into enantiopure materials by chiral HPLC with  $g_{lum} \approx 0.093$  at 775 nm.<sup>5e</sup> However, the neutral dqp and ddpd ligands lead to the emission of  $Cr(^2E/^2T_1 \rightarrow {}^4A_2)$ , which are only slightly tuneable. In addition, all these CPL-active Cr(III) complexes rely on chiral resolution processes, which become problematic in large scale preparation.


Our group has an interest in the employment of carboncentred chiral ligands to induce helical chirality complexes.<sup>10</sup> More recently, anionic tridentate N-donor ligands have been proven effective to lead to tuneable NIR emission in Cr(III) complexes, and the combination of  $\pi$ -donating amido with pyridine coordination units can achieve NIR-II luminescence at 1067 nm in frozen solutions at 77 K by increasing metalligand bond covalence. 4c,11 We herein report a series of Cr(III) complexes bearing carbazolyl-based tridentate ligands with carbon centred chirality in the hope of circumventing the reported homo-chiral helicities from the non-chiral ligand twist. In this way, we can achieve helical chiral Cr(III) complexes without the tedious chiral resolutions. We choose 1,8-(bisoxazolyl)carbazolide as the tridentate ligand, 12 in which the chiral bisoxazolyls are readily implanted from commercially available chiral aminoalcohols. For comparison, complexes with ligands exhibiting different positions of the chiral centres and nonchiral ligands were also prepared (Scheme 1 and ESI†).

Communication ChemComm

Scheme 1 Syntheses and chemical structures of 1S/1R, 2S/2R and 3.

Single crystals of 1S/1R and 3 were obtained by slow diffusion of *n*-hexane into the respective dichloromethane solution at ambient temperature and their structures were determined by X-ray crystallography (Fig. 1). The carbazole-based N(imido)-Cr-N(imido) bond angles (Table S4, ESI†) are 179.33(12)°-178.58(9)°, and the N(oxazolyl)-Cr-N(oxazolyl) bond angles are 176.55(11)°-174.87(9)°, revealing a more octahedral geometry than the reported [Cr(dpc)<sub>2</sub>]<sup>+</sup>. The Cr-N(imido) bond lengths (1.988(2)-1.999(2) Å) are shorter than the Cr-N(oxazolyl) bond lengths (2.040(2)-2.086(2) Å), which corresponds to the covalent nature of the Cr-N(imido) bond in the present structure. The two tridentate ligands coordinate in a meridional fashion to the central Cr(III) ion. The unit cell of 3 contained  $D_{2d}$  symmetrical enantiomeric PP and MM. In sharp contrast, due to the orientation of the chiral-methyl groups, the symmetry of 1S/1R results in lower  $D_2$  symmetry. For 1R, only the MM configuration was observed while in 1S, only the PP configuration was observed.

Complexes **1–3** show distinct X-band electron paramagnetic resonance (EPR) spectra which were measured in frozen acetonitrile at 100 K. Both **2** and **3** showed a prominent derivative signal at  $g \approx 2$  with some faint features at higher g values (Fig. 2), which is characteristic of Cr(III) species with small zero field splitting (ZFS,  $D < h\nu$ , D and E/D are the axial and orthorhombic zero-field parameters).<sup>13</sup> The weak signal at  $g \approx 5.9$  is assigned to the almost forbidden " $\Delta m = 3$ " transition

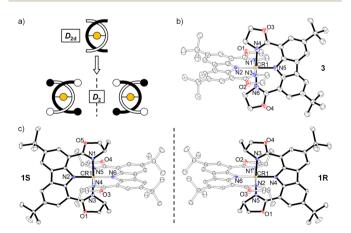

**Fig. 1** (a) Illustration of the chiral structures. Crystal structures of complexes (c) **1S/1R** and (b) **3**, drawn in 50% probability ellipsoids with H-atoms, counter-ions and solvate molecules omitted for clarity.




Fig. 2 EPR spectra of **1S**, **2R**, and **3** recorded in frozen acetonitrile at 100 K (concentration  $\sim 3.0 \times 10^{-3}$  M).

within the  $m_s = \pm 3/2$  Kramers doublet. <sup>13</sup> Interestingly, a broad derivative band at higher g values with extremely weak signal at  $g \approx 2$  was observed for 1 from the frozen solution. These features are in qualitative accordance with some Cr(III) species, which feature an electronic spin S = 3/2 with moderately large zero field splitting D and small rhombicity E (D >  $h\nu$ ,  $E/D \approx 0$ ). The spin-lattice interaction increases with the ZFS and therefore the signal diminishes at relatively low temperatures. 15 The g value of these Cr(III) species depends on spin-orbit interaction with excited spin quartet terms due to  $t_{2g} \rightarrow e_g$  excitations. It has been pointed out that the major contribution to the ZFS parameter D in the distorted octahedral symmetry comes from the  $^2E_{\rm g}$  excited doublet states.  $^{14}$  As a result, D is sensitive to the strength of the equatorial ligands. The small rhombicity observed of 1 surprisingly exhibits a different EPR signal compared with 2 and 3.16 In such a case, the EPR signals of 1-3 are primarily related to the stereoelectronic effect from the changes of the chiral steric groups.<sup>17</sup>

The photophysical properties of Cr(III) complexes 1-3 were explored using the ultraviolet-visible (UV-vis) absorption spectra and the fluorescence spectra. As expected, 1-3 display a similar pattern with two dominant bands between 250 and 350 nm ( $\epsilon \sim 4\text{--}8 \times 10^4 \text{ M}^{-1} \text{ cm}^{-1}$ ) which were assigned to ligand-centred  $\pi$ – $\pi$ \* transitions (Fig. 3a). The bands between 350 and 600 nm ( $\varepsilon \sim 1-3 \times 10^4 \, \mathrm{M}^{-1} \, \mathrm{cm}^{-1}$ ), corresponding to the lowest energy transitions, were tentatively assigned to metal-centred (MC) transition mixing with some ligand-tometal charge transfer (LMCT), according to previous studies. 4c,11a Upon excitation at 450 nm in degassed acetonitrile at 298 K, the emission peaks are at 845, 820 and 813 nm, respectively (Fig. 3d). The emission maximum of these Cr(III) complexes is insensitive to the polarity of the solvents (Fig. S19, ESI†). Unlike the sharp emission bands of other Cr(III) complexes which correspond to the spin-flip  $Cr(^2E/^2T_1 \rightarrow {}^4A_2)$ transitions, the broad emission bandwidth further implies spin-flip transition mixing with charge-transfer characters. 11a The decay curves (Fig. S20, ESI†) of emission intensity were fitted mono-exponentially to give the emission lifetime ( $\tau$ ) of 56.6, 259.4 and 266.7 μs for 1-3, respectively (Table S5, ESI†). The quantum yield  $(\Phi)$  was determined to be 2.4%, 7.5% and 8.2% for 1-3, respectively, in degassed acetonitrile at 298 K.

Although both 1S/1R and 2S/2R possess carbon-centred chirality, their electronic circular dichroism (ECD) signals show

ChemComm

Abs PL 400 900 600 700 700 λ/nm 50-ECD CPL Solution g<sub>lum</sub> ~ +0.002 800 900 1000 f) 40 0.010  $g_{abs}$ 30 20 0.005 -0.005 -30 ±0.003

Fig. 3 (a) Absorption spectra of 1S, 2S, and 3 in deaerated acetonitrile at 298 K (1.0  $\times$  10<sup>-5</sup> M). (b) Electronic circular dichroism of **1S/1R** and **2S/2R**  $(1.0 \times 10^{-5} \text{ M})$  in deaerated acetonitrile at 298 K. (c) Plots of absorption dissymmetry factor  $g_{abs}$  of 1S/1R and 2S/2R. (d) Emission spectra of 1S, 2S, and **3** in deaerated acetonitrile at 298 K (1.0  $\times$  10<sup>-5</sup> M). (e) CPL spectra of **1S/1R** and **2S/2R** ( $1.0 \times 10^{-4}$  M) in deaerated acetonitrile at 298 K. (f) CPL spectra of 1S/1R in the solid state at 298 K.

900

400

dramatic differences in the wavelengths of the peaks and corresponding intensity. The ECD spectra of 1S/1R exhibit an evident dichroic band at the lowest energy of 580 nm  $(\Delta \varepsilon = +7.2 \text{ M}^{-1} \text{ cm}^{-1} \text{ for 1S and } -11.1 \text{ M}^{-1} \text{ cm}^{-1} \text{ for 1R}) \text{ with }$ an absorption dissymmetry factor  $|g_{abs}|$  of 0.007 and 0.012 (Fig. 3b and c). The strong Cotton effects of 1S/1R at 510 and 580 nm are attributed to LMCT and metal-centred transitions, while the peaks below 350 nm correspond to ligand-centred transitions  $(\pi - \pi^*)$ . In the present case, the Cotton effect for 1 is more significant below 400 nm but with a lower  $|g_{abs}|$ . Meanwhile, 2S and 2R only show some weak ECD signals below 450 nm with infinitesimal  $|g_{abs}|$ .

Consistent with the ECD spectra, such an aspect is also clearly observed in the CPL spectra of these Cr(III) complexes. Upon nonpolarized excitation at 450 nm, the 1S and 1R display a pair of mirror NIR-CPL spectra between 700 and 1000 nm both in diluted deaerated acetonitrile and the solid state (Fig. 3e and f). The circularly polarized emission bands at 845 nm exhibit a  $g_{\text{lum}}$  value of +0.002 for 1S and -0.002 for 1R in degassed solution (Fig. S23, ESI†). In the solid state, the  $g_{\text{lum}}$  values of +0.003 for 1S and -0.003 for 1R were also obtained (Fig. S23, ESI $\dagger$ ). By contrast, the  $g_{lum}$  for complexes 2S/2R was almost zero in degassed solution. The sharp difference could be rationalised by the less crowded metal centre and less twisted helical chirality of 2S/2R when compared with those of 1S/1R. These experimental results revealed that the

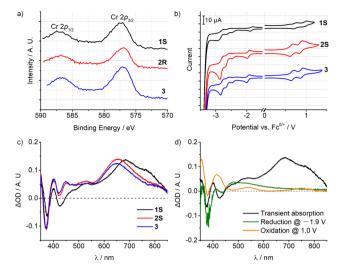


Fig. 4 (a) X-ray photoelectron spectra of 1S, 2R, and 3 showing the scan of the Cr 2p states. (b) Cyclic voltammograms of 1S, 2S, and 3 recorded in deaerated acetonitrile at 298 K (0.1 M <sup>n</sup>Bu<sub>4</sub>NPF<sub>4</sub> as supporting electrolyte, scanning rate  $100 \text{ mV s}^{-1}$ ). (c) Nanosecond transient absorption spectrum of **1S**, **2S**, and **3** (1  $\times$  10<sup>-4</sup> M in deaerated acetonitrile) at time zero after laser excitation. (d) Differential UV-vis absorption spectra of 15 in spectroeletrochemical experiments upon reduction at -1.9 V vs.  $\text{Fc}^{+/0}$  and upon oxidization at 1.0 V vs. Fc<sup>+/0</sup>, respectively, and their comparison with the nanosecond transient absorption spectrum of 15.

carbon-centred chirality-induced steric hindrance determines the twist degree of helical chirality as well as the  $g_{lum}$ , which also indicates that the  $g_{lum}$  can be further improved by using a more bulky carbon-centred chiral group. In addition, compared to the reported  $g_{\text{lum}}$  of  $\text{Cr}(^2\text{E}/^2\text{T}_1 \rightarrow {}^4\text{A}_2),^{5e-g}$  the lower  $g_{\text{lum}}$  of complexes 1S/1R further confirmed the mixing of electronically dipole-allowed charge-transfer transitions in the excited states.

Accordingly, the emissions of 1-3 are essentially metalbased transitions with some LMCT character, which is mainly dependent on the electronic effect of the ligand substituents. As shown in the X-ray photoelectron spectra (XPS), the Cr  $2p_{1/2}$ 2p<sub>3/2</sub> binding energies (eV) of 1-3 are 587.14/577.33, 586.84/ 576.96, and 586.78/577.02, respectively (Fig. 4a and Fig. S24, ESI†). The methyl groups at the oxazolyl units in complex 1 are closer to the metal centre, thus slightly increasing the electron binding energy of the Cr(III) ion and hence rendering it harder to be oxidized. Cyclic voltammetry (CV) also revealed a similar tendency (Fig. 4b). The first reduction potentials of 1-3 are reversible at around -2.0 V vs. Fc<sup>+/0</sup> which can be assigned to  $[Cr(L)_2]^{3+/2+}$ , and are much more negative than in  $[Cr(dpc)_2]^+$  $(E_{1/2} = -1.51 \text{ V } \text{vs. Fc}^{+/0})$ . The cathodically shifted potentials reflect the higher electron density at the metal centre, which is attributed to the stronger  $\sigma$ -donating nature of the oxazolyl units than pyridine. The oxidation potentials appear at +0.70 V vs. Fc<sup>+/0</sup> corresponding to the formal oxidations of  $[Cr(L)_2]^{4+/3+}$ , while the peak at ca. 0.90 V is assigned to the ligand oxidation, according to the CV measurement of the ligand precursor (Fig. S26-S28, ESI†). Combined with the modified structures, 1S shows a 0.1 V more positive potential, evidently reflecting the utilisation of the secondary coordination

Communication ChemComm

sphere on the oxazolyl subunit. And this is in conformity with the results of XPS measurements. By using ultraviolet photoelectron spectroscopy (UPS) (Fig. S25, ESI†), the HOMO energies were calculated to be -5.24, -5.44 and -5.46 eV for 1-3, respectively, which is also consistent with the electrochemical studies.19

The nanosecond transient absorption (TA) spectroscopy with spectro-electrochemical investigations further corroborates the admixture of LMCT character of the lowest energy excited state. Upon excitation at 355 nm with a nanosecond laser, the patterns of the TA spectra of 1-3 are very similar (Fig. 4c), featuring an excitedstate absorption (ESA) band peaking at 685 nm for 1 (655 nm for 2 and 650 nm for 3) and a weaker ESA band near 400 and 550 nm. Furthermore, a strong ground state bleach (GSB) at around 375 nm for 1-3 and a weak GSB at 425 nm for 1 were observed. For 1S, spectro-electrochemistry (Fig. 4d) at a potential of  $-1.9 \text{ V} \text{ vs. Fc}^{+/0}$ (inducing reduction of Cr<sup>3+/2+</sup>) yielded bleaches of the original absorption at around 375 nm and gave an additional weak absorption at 445-850 nm. Oxidation spectro-electrochemistry was performed by applying a potential of 1.0 V vs. Fc+0, corresponding to the oxidation of the ligand and the metal centre. The band at 380 nm is slightly bleached, and at the same time, strong absorption bands at 355 and 415 nm, and weak absorptions at 540 and 750 nm were also observed. The characteristic peaks of the TA spectra largely overlapped with the spectro-electrochemical difference spectra superposition of Cr3+/2+ reduction and ligand oxidation in the 350-600 nm range, <sup>20</sup> suggesting that the lowest-energetic excited state of 1 involves some LMCT character. However, the maximum ESA band peaking at 685 nm was missing in the spectroelectrochemical spectra.

In summary, Cr(III) complexes 1S/1R, 2S/2R and 3 have been prepared through the introduction of chiral oxazolyl in the backbones of the carbazole tridentate ligand. By simply changing the position of the carbon-centred chirality at the oxazolyl units, 1S/1R and 2S/2R show a dramatic difference of the degree of helical chirality, which is also reflected in  $g_{abs}$  and  $g_{lum}$ . The 1S/1R enantiomers show mirror-image CPL signals in the NIR region with the maximum  $g_{\text{lum}}$  value of  $2.0 \times 10^{-3}$ , while 2S/2R have almost no chiral optical activity. These results underline the interest of carbon-centred chiral ligands as a means to access chiral Cr(III) complexes. Our study provides an approach towards chiral Cr(III) complexes, which could achieve relatively high  $g_{lum}$  but avoid chiral resolution processes for NIR-CPL emitters.

This work was supported by the National Natural Science Foundation of China (21873044) and the Guangdong Major Project of Basic and Applied Basic Research (2019B030302009).

#### Conflicts of interest

There are no conflicts to declare.

#### Notes and references

- 1 (a) J. P. Riehl and F. S. Richardson, Chem. Rev., 1986, 86, 1; (b) G. Muller, Dalton Trans., 2009, 9692; (c) X. Zhang, J. Yin and J. Yoon, Chem. Rev., 2014, 114, 4918; (d) L. Cerdán, F. Moreno, M. Johnson, G. Muller, S. de la Moya and I. García-Moreno, Phys. Chem. Chem. Phys., 2017, 19, 22088; (e) K. Staszak, K. Wieszczycka, V. Marturano and B. Tylkowski, Coord. Chem. Rev., 2019, 397, 76; (f) D. W. Zhang, M. Li and C. F. Chen, Chem. Soc. Rev., 2020, 49, 1331; (g) L. E. MacKenzie and R. Pal, Nat. Rev. Chem., 2021, 5, 109; (h) X. Li, Y. Xie and Z. Li, Adv. Photonics Res., 2021, 2, 2000136.
- 2 (a) H. Xiang, J. Cheng, X. Ma, X. Zhou and J. J. Chruma, Chem. Soc. Rev., 2013, 42, 6128; (b) A. Zampetti, A. Minotto and F. Cacialli, Adv. Funct. Mater., 2019, 29, 1807623.
- 3 P. Vázquez-Domínguez, O. Journaud, N. Vanthuyne, D. Jacquemin, L. Favereau, J. Crassous and A. Ros, Dalton Trans., 2021, 50, 13220.
- 4 (a) R. Englman and J. Jortner, Mol. Phys., 1970, 18, 145; (b) S. F. Wang, B. K. Su, X. Q. Wang, Y. C. Wei, K. H. Kuo, C. H. Wang, S. H. Liu, L. S. Liao, W. Y. Hung, L. W. Fu, W. T. Chuang, M. Qin, X. Lu, C. You, Y. Chi and P. T. Chou, Nat. Photonics, 2022, 16, 843; (c) Y. Cheng, Q. Yang, J. He, W. Zou, K. Liao, X. Chang, C. Zou and W. Lu, Dalton Trans., 2022, DOI: 10.1039/ d2dt02872g.
- $5~\left(a\right)$  M. Penconi, M. Cazzaniga, S. Kesarkar, P. R. Mussini, D. Ceresoli and A. Bossi, Photochem. Photobiol. Sci., 2017, 16, 1220; (b) T. Biet, T. Cauchy, Q. Sun, J. Ding, A. Hauser, P. Oulevey, T. Bürgi, D. Jacquemin, N. Vanthuyne, J. Crassous and N. Avarvari, Chem. Commun., 2017, 53, 9210; (c) J. Song, M. Wang, X. Zhou and H. Xiang, Chem. - Eur. J., 2018, 24, 7128; (d) F. Zinna, L. Arrico and L. Di Bari, Chem. Commun., 2019, 55, 6607; (e) C. Dee, F. Zinna, W. R. Kitzmann, G. Pescitelli, K. Heinze, L. Di Bari and M. Seitz, Chem. Commun., 2019, 55, 1307; (f) J. R. Jiménez, B. Doistau, C. M. Cruz, C. Besnard, J. M. Cuerva, A. G. Campaña and C. Piguet, J. Am. Chem. Soc., 2019, 141, 13244; (g) J. R. Jiménez, M. Poncet, S. Míguez-Lago, S. Grass, J. Lacour, C. Besnard, J. M. Cuerva, A. G. Campaña and C. Piguet, Angew. Chem., Int. Ed., 2021, **60**, 10095,
- 6 (a) O. S. Wenger, J. Am. Chem. Soc., 2018, 140, 13522; (b) C. Wegeberg and O. S. Wenger, JACS Au, 2021, 1, 1860.
- 7 M. Poncet, A. Benchohra, J. R. Jiménez and C. Piguet, ChemPhoto-Chem, 2021, 5, 880.
- 8 C. Li and P. Duan, Chem. Lett., 2021, 50, 546.
- 9 (a) R. Carr, N. H. Evans and D. Parker, Chem. Soc. Rev., 2012, 41, 7673; (b) F. Zinna and L. Di Bari, Chirality, 2015, 27, 1.
- 10 J. Lin, M. Xie, X. Zhang, Q. Gao, X. Chang, C. Zou and W. Lu, Chem. Commun., 2021, 57, 1627,
- 11 (a) N. Sinha, J. R. Jiménez, B. Pfund, A. Prescimone, C. Piguet and O. S. Wenger, Angew. Chem., Int. Ed., 2021, 60, 23722; (b) N. Sawicka, C. J. Craze, P. N. Horton, S. J. Coles, E. Richards and S. J. A. Pope, Chem. Commun., 2022, 58, 5733.
- 12 T. Niwa and M. Nakada, J. Am. Chem. Soc., 2012, 134, 13538.
- 13 N. Shaham, H. Cohen, D. Meyerstein and E. Bill, J. Chem. Soc., Dalton Trans., 2000, 18, 3082.
- 14 T. Weyhermüller, T. K. Paine, E. Bothe, E. Bill and P. Chaudhuri, Inorg. Chim. Acta, 2002, 337, 344.
- 15 N. Clément, C. Toussaint, G. Rogez, C. Loose, J. Kortus, L. Brelot, S. Choua, S. Dagorne, P. Turek and R. Welter, Dalton Trans., 2010,
- 16 Y. Abe and H. Ogino, Bull. Chem. Soc. Jpn., 1989, 62, 56.
- 17 M. Jäger and H. B. Stegmann, J. Chem. Soc., Perkin Trans. 2, 1998,
- 18 S. Otto, M. Grabolle, C. Förster, C. Kreitner, U. Resch-Genger and K. Heinze, Angew. Chem., Int. Ed., 2015, 54, 11572.
- 19 L. Zheng, T. Zhu, W. Xu, L. Liu, J. Zheng, X. Gong and F. Wudl, J. Mater. Chem. C, 2018, 6, 3634.
- 20 N. Sinha, B. Pfund, C. Wegeberg, A. Prescimone and O. S. Wenger, J. Am. Chem. Soc., 2022, 144, 9859.