## Journal of **Materials Chemistry C**



**REVIEW** 

View Article Online



Cite this: J. Mater. Chem. C, 2024, 12, 10775

## Strategies for suppressing dark current of perovskite photodiodes towards reliable optoelectronic applications

Yue Wang, (1) \*\* Qing Song, (1) \*\* Deli Li, \*\* Yang Liu, \*\* Yang Wang (1) \*\* and Yonghua Chen \*b

Photodetection is crucial for advancements in next-generation technologies, including Internet of Things, intelligent perception, augmented and virtual reality, and human-machine interactions. Metal halide perovskites (MHPs) show unique properties that allow for the creation of straightforward diode structures, enabling efficient photogeneration and charge collection across a broad spectrum of wavelengths, from ionizing radiation to near-infrared. However, the presence of dark current  $(I_a)$  poses a significant challenge, affecting the performance of these devices. This review commences by outlining the essential performance measures impacted either directly or indirectly by  $I_d$ . Subsequently, it investigates the adjustable MHP materials employed in photodiodes, with a focus on their structural and morphological characteristics. We then explore the origins of  $I_d$  and highlight the crucial factors that impact the performance of MHP-based photodiodes (MHPPDs). Additionally, we examine various strategies to mitigate I<sub>d</sub>, thereby improving device efficacy. Finally, we provide insights into future directions for reducing  $I_d$  in MHPPDs, potentially leading to further enhancements in photodetection technologies.

Received 29th March 2024. Accepted 6th July 2024

DOI: 10.1039/d4tc01273a

rsc.li/materials-c

<sup>&</sup>lt;sup>b</sup> Key Laboratory of Flexible Electronics (KLOFE) & Institute of Advanced Materials (IAM), Jiangsu National Synergistic Innovation Center for Advanced Materials (SICAM), Nanjing Tech University (NanjingTech), 30 South Puzhu Road, Nanjing 211816, Jiangsu, China. E-mail: iamyhchen@njtech.edu.cn



Yue Wang

Yue Wang completed his BSc in Applied Physics from Tiangong University in 2012 and his PhD in Optical Engineering from Beijing Jiaotong University in 2018. He then worked as a postdoctoral fellow focusing on organic and perovskite-based photodetectors at the MIIT Key Laboratory of Flexible Electronics, Northwestern Polytechnical University until 2020. Currently, he is an associate professor at

Laboratory of Flexible Electronics (SLoFE) and Fujian Normal University, specializing in perovskite optoelectronics and flexible electronics applications.

## 1. Introduction

Photodetection is crucial in diverse fields, including medical Xray imaging, visible light capture, near-infrared medical imaging, short-wave infrared surveillance, and machine vision.<sup>1,2</sup> These applications fundamentally depend on semiconductor photodetectors to transduce photons into electrical signals for processing, image reconstruction, and storage. Commonly, photodiodes and phototransistors constructed from inorganic semiconductors of silicon or III-V compounds, when integrated with thin-film transistors (TFTs) or complementary metal oxide semiconductors (CMOS) within a backplane architecture, enable the creation of intricate image sensor arrays suitable for modern optoelectronics.3,4

The escalating demands of Internet of Things, intelligent perception, augmented and virtual reality, and humanmachine interactions necessitate components that are lightweight, energy-efficient, miniature, and mechanically flexible.<sup>5</sup> In response, researchers are exploring diverse semiconductorbased photodetectors, 6,7 including organic materials, inorganic nanocrystals (NCs), quantum dots (QDs), and metal-halide perovskites (MHPs). MHPs, in particular, have attracted substantial attention due to their remarkable capabilities. These materials offer an ultra-broad spectral photodetection range, from ionizing radiation to near-infrared, achievable through

<sup>&</sup>lt;sup>a</sup> Strait Institute of Flexible Electronics (SIFE, Future Technologies), Fujian Key Laboratory of Flexible Electronics, Fujian Normal University and Strait Laboratory of Flexible Electronics (SLoFE), Fuzhou, 350117, China. E-mail: ifeywang@fjnu.edu.cn, ifedlli@fjnu.edu.cn

tailored adjustments in their organic and inorganic compositions. MHPs are not only derived from abundant resources and require low deposition temperatures but also form efficient single layers owing to their low exciton binding energy.8 When integrated into optoelectronic systems, they substantively augment functionality and precision in various sensing applications, such as photoplethysmography (PPG) sensors and pulse oximeters, enabling real-time and non-invasive monitoring.

While MHP-based photoconductors and phototransistors are notable for their impressive responsivity, facilitating signal amplification across applications, they tend to have slower response times and usually require additional biasing circuits for optimal performance. These factors demand careful consideration, particularly in the context of specific applications. Despite these challenges, the intrinsic properties of MHPs support the creation of simplified diode architectures that promote efficient photogeneration and charge collection with minimal losses. MHPPDs, employing configurations such as P-N, P-I-N, or Schottky junctions, can function without an external power supply. Applying an additional reverse bias can further enhance the efficiency of photogenerated carrier collection. Moreover, the progress in MHP-based devices benefits extensively from ongoing research on perovskite photovoltaics. Consequently, significant research efforts are directed at advancing our understanding of materials, device architectures, physical mechanisms, and processing techniques in this field. This endeavor seeks to improve the figures of merits (FOMs) of MHPPDs to bring them on par with those of their counterparts.

A critical parameter affecting MHPPDs' FOMs directly or indirectly, including the on-off ratio (OOR), linear dynamic range (LDR), specific detectivity ( $D^*$ ), is the dark current ( $I_d$ ). In MHPPDs, as illustrated in Fig. 1, carriers in an MHP film tend to drift towards their respective electrodes in the absence of a bias voltage. This behavior, facilitated by the unique properties

of MHPs, leads to complete depletion even without an applied bias voltage, significantly impacting the device's performance. The OOR is defined as the ratio of the photocurrent generated when the photodiode is exposed to light (on-state) to  $I_d$  when it is not exposed to light (off-state). This ratio indicates how effectively a photodiode can distinguish between the presence and absence of light signals. Therefore, reducing  $I_d$  in MHPPDs while preserving the photocurrent can considerably enhance the OOR. The LDR represents a valuable feature for MHPPDs where the output, such as photocurrent or responsivity, remains stable across a broad spectrum of incident light intensities. Beyond this dynamic range, the light signals cannot be accurately detected due to the elevated levels of  $I_d$ .<sup>10</sup> Additionally, the noise equivalent power (NEP) defines the minimum optical power a photodiode can differentiate from the noise current, indicating the sensitivity of the photodiode to weak light signals. Noise current  $(i_n)$  in units of A  $Hz^{-1/2}$ primarily includes shot noise, thermal noise, and flicker noise, among which shot noise, arising from the discrete passage of electrons and holes, generally dominates. Thermal noise is linked to the random motion of charge carriers, and flicker noise can result from fluctuations in conductivity due to variations in the electron concentration. 11 Additionally, the influence of  $I_d$  in the practical industrial applications of photodiodes is substantial. For example, high  $I_d$  can rapidly reach the breakdown voltage of TFTs or CMOS, widely employed in imaging and sensing technology, rendering them ineffective.12

Furthermore, the  $I_d$  of MHPPDs plays a crucial role in direct radiation detection, specifically in X-ray imaging and ionizing radiation detection applications, enabling nondestructive inspection in medical, security, and scientific fields. In direct radiation X-ray detection, MHPPDs employ active layers with thicknesses up to millimeters to effectively block high-energy radiation photons, which raises the issue of less charge

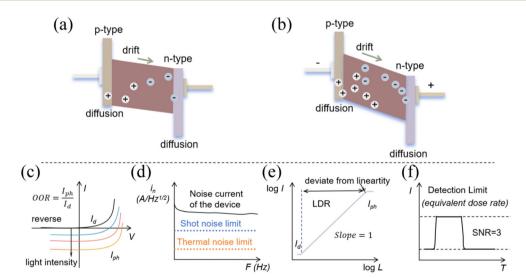


Fig. 1 Schematic illustration of the energy diagram of P-I-N photodiodes without bias (a) and under bias conditions (b). Schematic of the parameters influenced by  $I_{\rm d}$  in photodiodes for light sensing and direct X-ray detection. (c) On-off ratio (OOR). (d) Noise current ( $i_{\rm n}$ ). (e) Linear dynamic range (LDR). (f) Detection limit.

collection efficiency for the devices. One effective solution to overcome this challenge is operating MHPPDs at a high reverse bias, which unfortunately leads to a higher  $I_d$ . It can deteriorate the detection limit (refers to the lowest level of X-ray radiation that can be reliably detected) and the dynamic range of the ionizing radiation response of a detector. Furthermore, due to their low defect formation energies, the formed defects within MHPs are prone to ion migration when subjected to an electric field. As a result, the high reverse bias applied to MHPPDs in ionizing radiation applications can trigger a saturation period lasting hours, referred to as  $I_d$  drift, which affects the current long-term stability of MHPPDs, as these devices are typically operated at a specific reverse bias voltage relative to the reference  $I_d$ . The  $I_d$  drift can be calculated using: D =

 $\frac{I_{\rm finsh}-I_{\rm begin}}{tE}$ , where  $I_{\rm finish}$  and  $I_{\rm begin}$  are the final and initial dark currents, t is the test time, and E is the applied electric field.

Therefore, understanding the fundamental causes of  $I_d$  in MHPPDs is crucial. By exploring the elements that influence  $I_d$ , we can devise effective strategies to mitigate it, thus overcoming the challenges associated with the material composition and device architecture. Although recent literature 14 provides a thorough examination of  $I_d$ 's origins, limitations, and countermeasures in various MHP-based detectors like photodiodes, photoconductors, and phototransistors, there remains a gap concerning the specific issues of  $I_d$  in MHPPDs. Considering the significant impact of MHPPDs on the evolution of MHPbased photodetection technologies, further investigation in this area is essential. This review starts by defining the key performance metrics that are directly or indirectly influenced by  $I_d$ . It then examines the tunable MHP materials used in photodiodes, emphasizing their structural and morphological properties. We then explore the sources of I<sub>d</sub> and identify the key factors influencing  $I_d$  in MHPPDs. Additionally, we discuss various tactics to curb  $I_d$  in these devices. Finally, we contemplate future approaches to reduce I<sub>d</sub> in MHPPDs, underlining the necessity of developing a clear understanding of  $I_d$ 's mechanisms and exploring new avenues for research to diminish  $I_{\rm d}$  effectively.

# 2. Figures of merits of photodiodes and their relationship with dark current

In the following section, we provide a comprehensive definition of the key performance metrics that are directly or indirectly influenced by  $I_{\rm d}$ , thereby enabling a clear understanding of the reported MHPPD performances. A schematic illustration of several parameters affected by  $I_{\rm d}$  is shown in Fig. 1. For the most relevant metrics, we highlight their definitions and mathematical expressions, as well as their relationships with  $I_{\rm d}$ .

#### 2.1 Signal-to-noise ratio

In photodiodes, the signal-to-noise ratio (SNR) is a measure of the quality of the signal relative to the level of background noise. It is defined as the ratio of the photocurrent generated by the incident light (signal) to the noise current present in the system. Mathematically, the SNR can be expressed as:

$$SNR = \frac{i_{ph}}{i_n}$$

where  $i_{\rm ph}$  is the photocurrent resulting from the incident light, and  $i_{\rm n}$  is the total noise current. Since  $I_{\rm d}$  contributes to the shot noise, which is a significant component of the total noise current,  $I_{\rm d}$  directly affects the noise current and consequently impacts the SNR. A higher  $I_{\rm d}$  results in increased shot noise, which reduces the SNR. Furthermore, for simplicity, the OOR is often employed to gauge the sensitivity of photodiodes to light signals. It is calculated as the ratio of the photocurrent to the  $I_{\rm d}$ .

## 2.2 Spectral responsivity and EQE

The spectral responsivity (R) in units of A W<sup>-1</sup> describes how much current is generated by a photodiode per incoming photon of a given energy. It can be calculated using the formula:

$$R = \frac{J_{\rm ph}}{P_{\rm in}}$$

where  $J_{\rm ph}$  is the photocurrent density and  $P_{\rm in}$  is the incident light intensity. EQE, which denotes the ratio between the number of incoming photons and the number of photogenerated free electrons, can be expressed as:

$$EQE = R\frac{h\vartheta}{q}$$

where h is the Planck constant,  $\nu$  is the frequency of the incident photon, and q is the elementary charge. Generally, a high EQE (and hence R) is desirable to ensure efficient photon flux detection. In most cases, the EQE (or R) and  $I_{\rm d}$  are considered independent parameters. However, it is important to note that a high  $I_{\rm d}$  can lead to increased shot noise. This noise degrades the overall performance of the photodiode by making it more challenging to detect low-intensity signals accurately. This degradation can indirectly affect the effective EQE or (R) as well.

## 2.3 Speed

The speed of response, defined as the time required to collect photogenerated charge carriers at their respective contacts, ultimately determines the photodiode's dynamic range and cut-off frequency. Generally, the speed is evaluated based on the rise time  $(t_r)$  (the time it takes for the device response to increase from 10% to 90%) and the fall time  $(t_f)$  (the time it takes for the device response to decrease from 90% to 10%). The speed of response and  $I_d$  are both dependent on the intrinsic properties of the semiconductor materials, photodiode junction capacitance, and device operating temperature. For instance, high-quality semiconductors with fewer defects typically exhibit lower  $I_d$  and can also support faster response speeds. Conversely, high  $I_d$  can imply higher leakage in the junction, which may increase the junction capacitance.

Increased capacitance can slow down the response speed, as the photodiode takes longer to charge and discharge.

## 2.4 Noise equivalent power and specific detectivity $(D^*)$

The minimum incident light power that can be detected by a photodiode is referred to as the noise equivalent power (NEP). NEP is defined as the signal optical power that yields a SNR of 1. The NEP, expressed in units of W  $\rm Hz^{-1/2}$ , can be calculated using the formula:

$$NEP = \frac{i_n}{R\sqrt{B}}$$

where  $i_n$  is the noise current and B is the detection bandwidth. The specific detectivity  $D^*$  in units of cm  $\mathrm{Hz}^{1/2}\,\mathrm{W}^{-1}$  (or Jones) is the reciprocal of the NEP normalized to the square root of the device area A:

$$D^* = \frac{R\sqrt{AB}}{i_n}$$

As discussed,  $i_n$  primarily comprises shot noise, thermal noise, and flicker noise. Experimental measurements of  $i_n$  are challenging and not always performed. For simplicity, it is often assumed that the shot noise  $(i_{shot})$  from the  $I_d$  is the dominant contribution to  $i_n$ :

$$D^* \cong \frac{R\sqrt{AB}}{i_{\text{shot}}} = \frac{R\sqrt{A}}{\sqrt{2qi_{\text{d}}}}$$

This assumption implies that the  $I_{\rm d}$  (or  $i_{\rm shot}$ ) is the primary factor limiting  $D^*$ , while thermal noise and flicker noise are ignored. However, in photodiodes, and particularly in MHPPDs,  $i_{\rm n}$  is not solely equivalent to  $i_{\rm shot}$ , especially at low frequencies. Thus, this simplification can lead to an overestimation of  $D^*$ .

#### 2.5 Linear dynamic range

In photodiodes, the linear dynamic range (LDR) is a specification that indicates the range of incident light intensities over which the photodiode can produce a linear (proportional) response in terms of the output photocurrent. Essentially, it quantifies the operational light intensity span of the image sensor. It is defined as the ratio between the maximum detectable photocurrent before saturation and the minimum detectable photocurrent above the noise floor. Mathematically, the LDR can be expressed in decibels (dB) as:

$$LDR = 10 \log \left( \frac{I_{\text{max}}}{I_{\text{min}}} \right)$$

where  $I_{\rm max}$  is the maximum photocurrent that the photodiode can handle linearly, limited by the onset of saturation.  $I_{\rm min}$  is the minimum photocurrent that can be detected above the noise floor, dominated by the  $I_{\rm d}$  and other noise sources. A higher  $I_{\rm d}$  increases the noise floor, thus raising the minimum detectable photocurrent  $I_{\rm min}$ . Consequently, this reduces the LDR because: as  $I_{\rm min}$  increases, the ratio  $I_{\rm max}/I_{\rm min}$  decreases. This ratio determines the LDR, so an increase in  $I_{\rm min}$  directly reduces the LDR.

# 3. Metal halide perovskites for photodiodes

Typically, MHPs have the general formula ABX3, where A represents monovalent cations such as CH<sub>3</sub>NH<sub>3</sub><sup>+</sup> (MA), HC(NH<sub>2</sub>)<sub>2</sub><sup>+</sup> (FA), cesium (Cs<sup>+</sup>), and rubidium (Rb<sup>+</sup>) or their combinations. B refers to divalent metal cations such as Pb<sup>2+</sup>, Sn<sup>2+</sup>, Bi<sup>2+</sup>, and Ge<sup>2+</sup>, while X represents halide anions such as Cl<sup>-</sup>, Br<sup>-</sup>, and I<sup>-</sup> or a combination thereof. By adjusting the components, structure, and morphology, the optical absorption and electrical properties of MHPs can be easily modified. For example, as the ionic radius of the A cation increases  $(r_{Cs}^{+} <$  $r_{\rm MA}^+ < r_{\rm FA}^+$ ), the lattice expands, and the bandgap decreases, leading to a red shift in the optical absorption band. Another way to tune the bandgap is by replacing Pb<sup>2+</sup> with Sn<sup>2+</sup>, which reduces the bandgap and extends the optical absorption edge into the near-infrared (NIR) region. Successive tuning of the bandgap of MHPs can also be manipulated by changing the halide composition. As shown in Fig. 2a, the halide composition changes from Cl- to Br- to I-, and the bandgap sequentially decreases, allowing MHPs to absorb a broader range of light from ultraviolet (UV) to visible wavelengths. 15 Furthermore, MHPs composed of Pb, Bi, I, and Br are promising for direct radiation detection due to the high atomic number of these elements, providing excellent potential for quick X-ray direct detection.16

The structure dimensionality of MHPs can be tuned from three-dimensional (3D) bulk materials to two-dimensional (2D) layered structures and one-dimensional (1D) chain materials by manipulating the connections of [BX<sub>6</sub>]<sup>4-</sup> octahedral units (as shown in Fig. 2b). For instance, 2D MHPs are formed by incorporating larger organic cation layers between the octahedral network of 3D MHPs. This can be expressed as a general formula  $(LA)_m(A)_{n-1}B_nX_{3n+1}$ , where LA represents the larger organic cation and n denotes the number of layers in the 2D MHP structure. Introducing these larger organic cations in lowdimensional MHPs enhances their moisture stability and mechanical flexibility compared to their 3D counterparts. However, it should be noted that these long-chain organic cations also decrease the dielectric constant of MHPs, leading to an increase in the exciton binding energy. Consequently, the efficient separation and extraction of photogenerated carriers can be impeded. 19

Moreover, the control over the morphology dimensionality of MHPs enables the incorporation of novel properties into these materials. (Fig. 2b) For instance, 0D MHP nanostructures such as NCs and QDs exhibit tunable sizes ranging from several to tens of nanometers. These nanostructures generally possess large extinction coefficients and demonstrate characteristics of multiple-exciton generation. On the other hand, 1D MHP micro/nanostructures, including nanowires (NWs) and nanorods (NRs), feature significant surface-to-volume ratios and anisotropic geometries. These attributes contribute to low defect/trap densities, prolonged charge-carrier lifetimes, and reduced carrier recombination rates. Furthermore, 2D MHPs, comprising nanoplates, nanoflakes, and nanosheets,

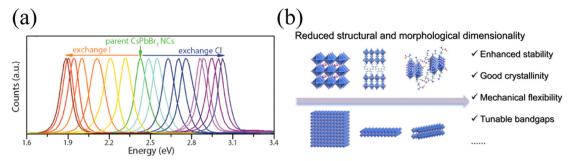


Fig. 2 (a) Bandgaps of MHPs (CsPbBr<sub>3</sub> nanocrystals) can be tuned by changing halide components. Reproduced with permission. <sup>17</sup> Copyright 2015, ACS. (b) Optical and electrical properties can be tuned by the tunable dimensionality at the structural and morphological level of MHPs. Reproduced with permission.<sup>18</sup> Copyright 2021, ACS.

exhibit strong quantum confinement effects and possess unique morphological characteristics. Additionally, these lowdimensional MHP materials demonstrate reasonable mechanical flexibility due to their atomic thickness. However, the nanostructures of low-dimensional MHPs still encounter issues that hinder charge transport and extraction in photodiodes. For instance, an excess of long-chain organic ligands on the surfaces of 0D and 2D MHPs can obstruct carrier transport, leading to reduced charge transfer efficiency. Moreover, the random orientation and rough morphology of 1D and 2D MHPs may create leakage paths, further impeding charge extraction. While 3D MHP polycrystalline materials have demonstrated remarkable improvements in photovoltaics due to their superior optoelectronic properties, overcoming challenges related to hysteresis and stability remains an ongoing endeavor.<sup>21</sup>

## 4. The origin of dark current in **MHPPDs**

## 4.1 Understanding dark current in MHPPDs

Typically, photodiodes are operated under reverse bias, so  $I_d$  is also known as reverse saturation current. In the following part, dark current density (J<sub>d</sub>) is investigated by considering the device area in a photodiode. In photodiodes,  $J_d$  flow of majority carriers can be impeded by the interfacial barrier of P-N junctions. Thus,  $J_d$  in MHPPDs comprises several components: diffusion current  $(J_{\text{diff}})$ , influenced by thermodynamics; generation-recombination current  $(J_{g-r})$ , determined by various recombination processes such as trap-assisted recombination, Auger recombination, and radiative recombination; and tunneling current (trap assisted tunneling, TAT) and leakage current, influenced by traps present in the absorption layer and at the interface between the absorber materials or electrodes and subsequent transport layers, as shown in Fig. 3.

According to the following equation,  $J_{\text{diff}}$  of a semiconductor-based photodiode is determined by thermodynamics, such as the carrier density and bandgap of the materials used:

$$J_{\rm diff} = q N_{\rm c} N_{\rm v} \Biggl( \frac{1}{N_{\rm A}} \sqrt{\frac{D_{\rm n}}{\tau_{\rm n}}} + \frac{1}{N_{\rm D}} \sqrt{\frac{D_{\rm p}}{\tau_{\rm p}}} \Biggr) {\rm exp} \Biggl( -\frac{E_{\rm g}}{k_{\rm B} T} \Biggr)$$

where  $D_{\rm p}$  and  $D_{\rm n}$  are the diffusion coefficients of holes and

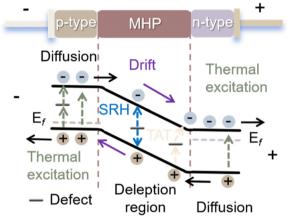


Fig. 3 The typical components and generation mechanisms of dark current in MHPPDs

electrons, respectively.  $N_{\mathrm{D}}$  and  $N_{\mathrm{A}}$  represent the donor and acceptor concentrations on the n side and p side, respectively.  $N_c$  and  $N_v$  denote the effective density of states for electrons in the conduction band and holes in the valence band, respectively;  $\tau_p$  and  $\tau_n$  are the carrier lifetimes of holes and electrons, respectively.  $J_{\text{diff}}$  in a photodiode increases with temperature and decreases as the material quality increases.

The type of contact can influence  $J_{\rm diff}$ . In the case of a Schottky contact, where the depletion region serves as the barrier layer,  $J_{\text{diff}}$  consists of various components. One of these components is the thermionic-emission current  $(J_T)$ , which can be calculated using the Richardson-Dushman equation based on the thermionic-emission theory. This equation helps determine the contribution of thermionic emission to the overall  $J_{
m diff}$ : 22

$$J_{\rm T} = AT^2 e^{-\frac{q\varphi_{\rm s}}{kT}} \left( \frac{qV}{e^{kT}} - 1 \right)$$

The Richardson constant, denoted by A, has a value of 120 A  $(cm^{-2} K^{-2})$  for vacuum. It reflects the relationship between the temperature, area, and the thermionic-emission current. The term  $q\varphi_s$  represents the barrier height for carrier injection in the Schottky contact. Any changes in the Schottky barrier height  $(\varphi_s)$  affect  $J_T$ , the main contributor to  $J_{\text{diff}}$  in this contact

configuration. On the other hand, in the case of an Ohmic contact where the depletion region acts as the accumulation layer,  $J_{\text{diff}}$  arises from a combination of carrier thermionicemission and diffusion processes. Theoretically, introducing blocking layers with high enough barriers between materials and electrodes makes achieving low  $J_{\text{diff}}$  in the P-N junction possible.

Another significant source of  $J_d$  is the generationrecombination current  $(J_{g-r})$ , which arises from both the bulk depletion region and the interface. According to the Shockley-Read-Hall (SRH) model,  $J_{g-r}$  is determined in the bulk layer:<sup>23</sup>

$$J_{g-r} = \frac{qn_i X_{d}}{2\tau} \left( e^{\frac{qV}{2kT}} - 1 \right)$$

in addition to the factors mentioned earlier,  $J_{\rm g-r}$  depends on the intrinsic carrier concentration  $(n_i)$  and the non-equilibrium carrier lifetime  $(\tau)$ , which is inversely related to the trap concentration  $(N_t)$ .  $J_{g-r}$  is directly proportional to both  $N_t$  and the depletion region width  $(X_d)$ . Unlike  $J_T$ ,  $J_{g-r}$  cannot be suppressed by the Schottky barrier alone. However, by reducing the concentration of traps in the semiconductor material,  $I_{g-r}$ can be effectively suppressed. This highlights the importance of minimizing trap concentrations to achieve low  $J_d$ .

Aside from charge injection and bulk thermal generation of charge carriers, tunneling and leakage current processes also affect  $I_d$  in photodiodes. Photodiodes typically consist of multiple layers, including an absorber and a charge transport layer. Suppose traps are present in the absorber layer, in that case, trap-assisted tunneling can occur between the valence and conduction bands of the absorber materials or between the absorber materials and subsequent transport layers, increasing  $J_d$ .

### 4.2 Advancements in exploring dark current mechanisms in **MHPPDs**

In the context of MHPPDs, investigating the factors that influence  $J_d$  is essential for elucidating its origin. Researchers have identified that one of the primary origins of  $J_d$  in MHPPDs is the migration of ions through the bulk of the grains via point defects or extended defects, such as grain boundaries, which are considered material imperfections specific to MHPPDs. A study conducted by Jang et al. compared MHPPDs based on Pb and Sn MHP films. The researchers discovered that vertical grain boundaries in these materials contribute to increased  $I_d$ , while horizontal grain boundaries have the opposite effect of reducing  $J_d$ .<sup>24</sup> This disparity can be attributed to smaller grains in the Sn-based MHPs, resulting in divergent shunt pathways for  $J_d$ . (Fig. 4a) Consequently, Yang et al. conducted a study in which they observed a decrease in the  $J_d$  of MHP films containing potassium salt additives by reducing the crystal grain size of Sn-based MHPs. This reduction in  $J_d$  was attributed to the increased presence of shunting paths.25 Furthermore, the inherently weaker halide-ion migration in the Sn-based material provides an advantage in suppressing  $J_d$ . Similarly, Dey et al. conducted an investigation using scan-rate-dependent hysteresis analyses, temperature-dependent impedance spectroscopy measurements, and first-principles calculations on mixed Pb-Sn MHPs.26 Their research revealed the crucial role of Sn vacancies in enhancing the migration barrier of iodide ions, which occurs due to local structural distortions. Yin et al. conducted a study highlighting the significant contribution of surface iodine vacancies to  $J_d$  in polycrystalline MHPPDs.<sup>27</sup> Their experimental findings revealed that the trap states induced by surface iodine vacancies within the bandgap can create many generation and recombination centers. Consequently, this leads to a decrease in the minority carrier lifetime and an increase in the generation-recombination current density based on the SRH mechanisms under dark conditions (Fig. 4b). Moreover, Moseley et al. underscored the significance of considering the presence of defects in MHP films, which can result in  $J_d$  that exhibit time-dependent drifting over seconds, as they can cause measurement challenges such as speed and LDR. 28 These defects and trap states can generate a photoconductive gain by extending carrier lifetimes beyond transit times or altering interface energetics, enabling charge injection even under low light intensity in MHPPDs.

In addition to the presence of structural and compositional imperfections such as pinholes, trap states, and grain boundary leakage in MHPs, the contact between the MHPs and the charge transport layers (CTLs) or electrodes also significantly influences the experimental  $J_d$  of MHPPDs. Sutherland et al. observed that MHPPDs and MHP-based solar cells exhibit differences in their reverse saturation current density.<sup>31</sup> Given

that 
$$V_{\rm oc} = nKTq^{-1} \ln \left[ \frac{\left( J_{\rm sc} - \frac{V_{\rm oc}}{R_{\rm sh}} \right)}{J_0} + 1 \right]$$
, shunt paths are not

crucial in limiting  $V_{\rm oc}$  (open-circuit voltage) until  $R_{\rm sh}$  (shunt resistance) becomes extremely small. Shunt paths of this magnitude can immensely increase  $J_d$  under reverse bias. Thus, it is not always guaranteed that the efforts to optimize solar cell performance will result in sufficiently low  $J_d$  for effective photodetection. They further developed the electron contact composites ( $TiO_2/Al_2O_3/PCBM$ ) for MHPPDs to minimize  $J_d$ . Duijnstee et al. discovered that the experimental data must consider an interface injection barrier to fit the TPC measurement.32 They pointed out that the injection barrier and ionization of trapped carriers at the interface contribute to the  $J_d$ . Moreover, Ollearo et al. demonstrated that the interfacial energy offset between the electron-blocking layers and the MHPs significantly determines the magnitude of  $J_d$ .<sup>29</sup> As the offset increases, it can efficiently suppress the thermal charge generation at the interface between electron-blocking layers (EBL) and the MHPs, leading to a significantly lower  $I_d$ (Fig. 4c).

### 4.3 The dark current drift in MHPPDs

The  $J_d$ 's saturation period under reverse bias conditions commonly known as instabilities in the dark reverse saturation current can lead to measurement inaccuracy in MHPPDs, especially for direct radiation detection. It is worth mentioning that other halide-based radiation detectors under the high

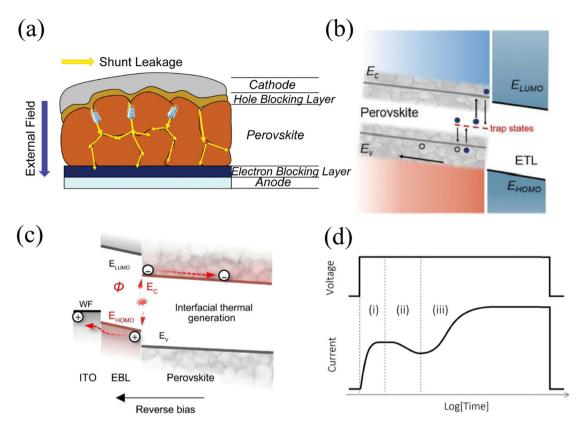



Fig. 4 (a) Diagram illustrating the formation of multiple divergent leakage pathways in a Sn-based MHP with a reduced grain size. Reproduced with permission.<sup>24</sup> Copyright 2022, Wiley-VCH. (b) Schematic energy level diagram showing the generation–recombination processes enhanced by surface trap states under dark conditions. Reproduced with permission.<sup>27</sup> Copyright 2023, Wiley-VCH. (c) Schematic representation of the thermal charge generation mechanism at the EBL-MHP interface. Reproduced with permission.<sup>29</sup> Copyright 2021, Nature. (d) Schematic regime of long-term dark reverse bias current response for MHPPDs. Reproduced with permission.<sup>30</sup> Copyright 2022, Wiley-VCH.

reverse bias conditions also face the problem of  $J_d$  drift.<sup>33</sup> Recent studies have highlighted two leading causes for the  $J_d$ drift in MHP films used in direct radiation detection. Firstly, the presence of mobile ions within the bulk and grain boundaries of MHP films can contribute to the drift.<sup>34</sup> Secondly, the trapping or accumulating charge carriers at interlayers can also lead to the drift phenomenon. Several techniques and models have been employed to investigate and predict the transient  $J_d$ decay characteristics associated with the trapping or accumulating charge carriers at interlayers. Different MHP absorbers and interlayer materials have been studied in this regard.<sup>35–37</sup>

Understanding the ionic conduction in MHPs, in terms of electronic and ionic behaviors, is crucial in comprehending the  $J_{\rm d}$  drift regarding ion migration process. Yang et al. studied MA<sub>1-x</sub>FA<sub>x</sub>PbI<sub>3</sub>, a mixed electronic/ionic material, they discovered that halide (iodine) migration occurs under an electric field in such materials by measuring and modeling the stoichiometric polarization by the mixed conduction.<sup>38</sup> Investigating ion mobility in different MHPs is significant due to their known halide ion-conducting properties under dark conditions. García-Batlle et al. conducted a comparative analysis of two compounds, namely MAPbBr3 and MAPbI3, along with different structures, such as single-crystalline and microcrystalline, to study the long-term evolution of  $J_d$ .<sup>39</sup> To estimate the ion mobility in these systems, they employed ionic time-offlight measurement techniques and obtained values ranging from  $10^{-7}$  to  $10^{-6}$  cm<sup>2</sup> V<sup>-1</sup> s<sup>-1</sup>. The results revealed that bromide compounds exhibited lower ion mobility, dependent on the electric field. Conversely, iodide compounds showed higher ion mobility, independent of the electric field. In addition, Almora et al. performed MATLAB code driftfusion simulations to investigate the long-term reverse bias current behavior in MHPPDs.<sup>30</sup> (Fig. 4d) Their findings revealed that the steadystate  $J_d$  observed under reverse bias is primarily an electronic current rather than an ionic current, even though the presence and concentration of mobile ions play a crucial role. The reduction of  $J_d$  drift through screening is influenced by the following factors: the thickness of the MHPs, the applied electric field, the concentration of mobile ions, and the mobile ion mobility. By employing material engineering techniques such as composition and interface engineering in MHPs, it is possible to reduce the screening of  $J_d$  drift.

## 5. Strategies for suppressing dark current toward high performance MHPPDs

Comprehending the components and underlying mechanisms of  $J_d$  in photodiodes is crucial for understanding their operational behavior. This knowledge facilitates the development of

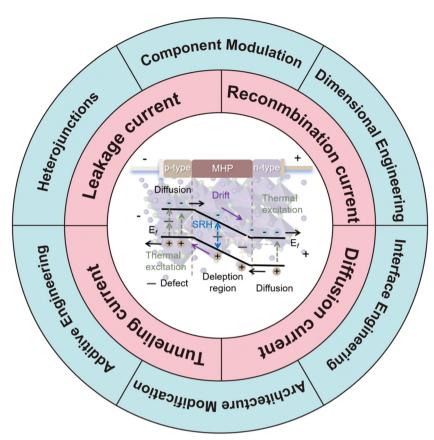

Schematic illustration of the components of  $J_{\rm d}$  and the methods for suppressing the  $J_{\rm d}$  of MHPPDs.

targeted strategies to mitigate  $J_d$  in MHPPDs. For instance, operating these devices at lower temperatures can effectively reduce the intrinsic carrier concentration within the MHP film, which serves to suppress  $J_{\text{diff}}$ . Additionally, employing techniques such as compositional modulation and bulk passivation can enhance the MHP film quality and reduce inherent material defects, thereby diminishing  $J_{g-r}$ . Furthermore, employing interfacial engineering strategies, including the use of insertion layers or passivation techniques, can crucially curb surface or interfacial defects. This, in turn, helps to decrease  $I_d$  associated with trap-induced carrier generation and recombination. The application of heterojunctions allows for the integration of MHP with other materials, promoting optimal band alignment, reducing surface defects, and tuning related optical and electrical properties. Such alignment, aided by the built-in potential, acts as a barrier against the flow of majority carriers to decrease  $J_{\text{diff}}$ . Moreover, modifications in device architecture can influence carrier transport mechanisms and promote band bending, which further prevents carrier recombination. In the following section, we delineate comprehensive strategies for mitigating  $J_d$  in both the material composition and device structure to boost performance and ensure the reliability of optoelectronic applications, as shown in Fig. 5.

## **Component modulation**

As ionic crystals, MHPs exhibit formation energies for anion/ cation vacancies that are largely influenced by Coulomb interactions between the ions and crystal frameworks. By precisely controlling the composition of MHP crystals, it becomes feasible to enhance bonding energy, alleviate stress, optimize morphology and crystallinity, and significantly decrease  $J_d$ .

For instance, as shown in Fig. 6(a)-(c), Yun et al. investigated the engineering of A-site monovalent cations in wide-bandgap MHPs for high-performance blue photodetection. 40 Their findings revealed that introducing FA in MA increased the heat of formation, leading to modulated nucleation and grain growth behavior. Furthermore, the incorporation of optimal Cs (5%) helped mitigate strain and decrease trap states in the MHP thin film, resulting in a more compact and better-arranged crystal lattice. These improvements enabled the fabrication of N-I-P devices with a decent  $D^*$  of 5.08  $\times$  10<sup>12</sup> Jones, and demonstrated the feasibility of individual  $7 \times 7$  devices for real image sensing under 450 nm blue light illumination. Additionally, Liu et al. explored the modulation of A-site monovalent cations and X-site halide anions in MHPPDs for direct X-ray detection. 41 They observed that smaller cations (MA<sup>+</sup> and Cs<sup>+</sup>) and anions (Br<sup>-</sup>) resulted in the release of lattice stress and improved morphology, as evidenced in Fig. 6d. The optimized composition of FA<sub>0.85</sub>MA<sub>0.1</sub>Cs<sub>0.05</sub>PbI<sub>2.55</sub>Br<sub>0.45</sub> exhibited superior properties, including an ultra-low trap density of  $(4.6 \pm 2.4) \times$ 10<sup>9</sup> cm<sup>-3</sup>, a long carrier lifetime of 6.4 μs, and a diffusion length of 68.9 µm. This composition achieved an extremely low  $J_{\rm d}$  of  $-1.44~\mu{\rm A~cm}^{-2}$  at  $-75~{\rm V}$  bias, and a low detection limit of 42 nGy<sub>air</sub> s<sup>-1</sup>. Furlan et al. demonstrated the tunable halide

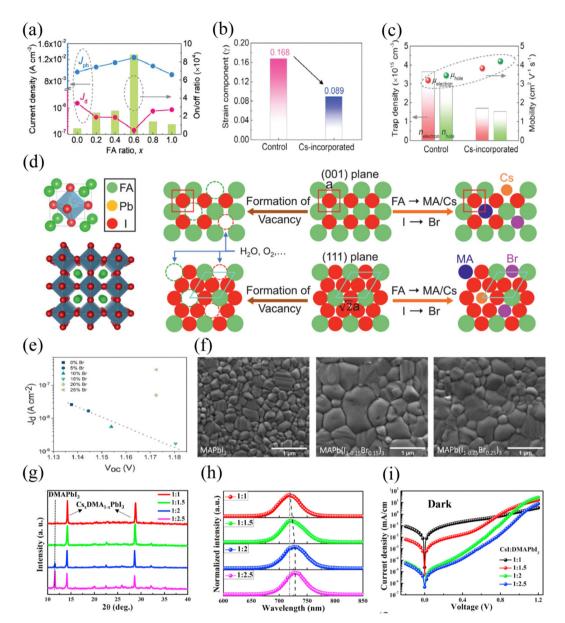


Fig. 6 (a)  $J_{d'}$ , and photocurrent density, and on/off ratio with the different FA/MA ratios. (b) Strain components of control and Cs-incorporating MHP films. (c) Trap density and mobility of control and Cs-incorporating MHP films obtained from the electron/hole-only configuration. Reproduced with permission. 40 Copyright 2022, Wiley-VCH. (d) Schematic illustration of the lattice stress release of the 3-cation mixed-halide FAMACs MHPs. Reproduced with permission. 41 Copyright 2020, Wiley-VCH. (e) The relationship between  $J_d$  and  $V_{oc}$  with various halide Br and I ratios. (f) Surface morphology of MAPb(I<sub>1-x</sub>Br<sub>x</sub>)<sub>3</sub> MHP thin films obtained by scanning electron microscopy. Reproduced with permission. <sup>42</sup> Copyright 2022, Wiley-VCH. (g) and (h) XRD patterns and PL spectra of the  $Cs_xDMA_{1-x}Pbl_3$  films. (i) J-V curves of MHPPDs in the dark based on the  $Cs_xDMA_{1-x}Pbl_3$  films. Reproduced with permission.<sup>43</sup> Copyright 2020, Elsevier.

composition in organic cation-based MHPs. 42 By adding Br to MAPbI<sub>3</sub>-based MHPs, they not only adjusted the bandgap through lattice contraction but also reduced non-radiative recombination losses in MHP layers by tuning the crystallite size, as shown in Fig. 6f. They established a correlation between the reduced  $J_{\rm d}$  (1.3 × 10<sup>-9</sup> A cm<sup>-2</sup> at -0.5 V),  $V_{\rm oc}$  enhancements (Fig. 6e), and achieved high-performance MHPPDs ( $D^*$  of 8.7  $\times$ 10<sup>12</sup> Jones) within the range of 350-850 nm. Although inorganic MHPs (CsPbX<sub>3</sub>) are suitable for high-performance and stable photodetection applications, they also exhibit thermodynamic instability at room temperature and spontaneously transform into a photo-inactive phase under ambient conditions due to the small tolerance factor. Li et al. demonstrated high-performance MHPPDs with an ultra-low  $J_{\rm d}$  (6.4  $\times$  $10^{-5}$  mA cm<sup>-2</sup>) (Fig. 6i) and a high speed of 558 ns by utilizing the organic cation DMA (DMA+ = dimethylammonium, (CH<sub>3</sub>)<sub>2</sub>NH<sub>2</sub><sup>+</sup>) to enhance the room-temperature phase stability of Cs-based MHP thin films. 43 The blue shift of the diffraction peak position observed in Fig. 6g was attributed to the introduction of DMA<sup>+</sup>, which has a larger ionic size than Cs<sup>+</sup>. In

addition, this finding was supported by the photoluminescence spectra (PL) of the Cs<sup>+</sup> and DMA<sup>+</sup>-based MHP films.

In addition to the effective modulation of A-site and X-site components to reduce  $J_d$  and improve device performance, researchers have also been exploring B-site regulation. For instance, hybrid Pb-Sn MHP-based MHPPDs have been investigated to achieve a broad spectral response ranging from 300 nm to 1000 nm, while also reducing Id compared to Pb-based devices, thanks to the reduced trap density.44 Furthermore, researchers have conducted halide composition modulation to develop nontoxic bismuth MHPs. 45 All of these demonstrations highlight the significant potential of component modulation in MHPs for effectively suppressing  $I_d$  and enhancing device performance. An update on the progress in the reported component modulation of the MHPPDs is provided in Table 1.

#### 5.2 Dimensional engineering

Numerous studies have shown that effective dimensional regulation of MHPPDs using hydrophobic organic cations can reduce the dimension of MHPs and transition them from 3D to quasi-2D structures. This not only helps suppress defects, thanks to the high defect formation energies of quasi-2D MHPs, but also significantly improves their stability. Thus, efforts have focused on creating a quasi-2D MHP layer at the interface, forming a 2D/3D MHP structure. 27,53-55

approach leads to fewer trap states at the MHP and electrode interface, consequently improving device performance. However, it is important to note that excessive presence of 2D MHPs at the interface, as well as disordered phase distribution, can impede charge transport due to the insulating effect of the bulkier, long-chain organic spacer cations (as illustrated in Fig. 7a). Recent efforts have therefore aimed at creating uniformly distributed, compact 2D-3D gradient MHPs with an ordered phase distribution along the thin film's longitudinal direction, as this offers enhanced optoelectronic properties, stability, and ideal MHPPD characteristics. For instance, Miao et al. employed the hot-casting method to control the phase distribution of quasi-2D MHP thin films.<sup>56</sup> By comparing the top and bottom PL spectra of different MHP thin films (as shown in Fig. 7b), they studied the effects of substrate temperature on surface morphology and internal phase distribution. The resulting device showed an extremely low  $J_d$  (2.3  $\times$  $10^{-11}$  A cm<sup>-2</sup>), large D\* at 455 nm (1.22 ×  $10^{14}$  Jones), ultra-fast speed (5.5/4.7 µs), and remarkable stability. Additionally, Peng et al. reported an ion-exchange strategy to prepare 2D-3D thick MHP films with uniform morphology, vertically aligned monolithic crystal phases, and reproducibility (as shown in Fig. 7c).<sup>57</sup> By performing an ion exchange between Br and I halide anions, they achieved a slow crystallization process resulting in a gradient phase distribution of 2D-3D MHP thick films. In situ

**Table 1** Summary of the component modulation in bulk MHPs for suppressing  $J_d$  and enhancing the FOMs of MHPPDs

Strategy	Device structure	Dark current (density) ( $I_{\rm d}$ or $J_{\rm d}$ )	D* (Jones)	Speed [rise time $(t_r)$ / fall (decay) time $(t_f)$ ]		
Reduce bulk defects (rubidium incorporated into FAPbI <sub>3</sub> )	ITO/PEDOT:PSS/ MHP/C <sub>60</sub> /BCP/Cu	$10^{-10}$ A cm <sup>-2</sup> (0 V, about 100 times reduced)	$1.7 \times 10^{12}$	300/— ns	125	46
Alleviate stress and reduce bulk defects (Cs incorporated into FAPbI <sub>3</sub> )	ITO/MeO-2PACz/ MHP/C <sub>60</sub> /BCP/Ag	$3.3 \times 10^{-9} \text{ A cm}^{-2} (-0.5 \text{ V})$	$6.1\times10^{11}$	1.2/1.2 μs	135	47
Optimize morphology and crystallinity (Cs and Br optimization in FAPbI <sub>3</sub> )	ITO/MoO <sub>3</sub> /TaTm/ MHP/C <sub>60</sub> /CN- T2T:C <sub>60</sub> /Ag	$8.627 \times 10^{-10} \text{ A cm}^{-2} (0 \text{ V})$	$1.747 \times 10^{13}$ (530 nm)	629/616 ns	127	48
Alleviate stress and reduce bulk defects (Cs, MA, FA optimization in $\mbox{APbBr}_2\mbox{Cl})$	ITO/SnO <sub>2</sub> /MHP/ PMMA/Spiro- OMeTAD/Au	$3.04 \times 10^{-8} \text{ A cm}^{-2} (0 \text{ V})$	$5.57 \times 10^{12}$	585/531 μs	_	40
Optimize morphology and crystallinity (Br, Cl, I optimization in MAPbX <sub>3</sub> )	, ITO/SnO <sub>2</sub> /MHP/ Spiro-OMeTAD/Au	$2.7 \times 10^{-7} \text{ A cm}^{-2} (0 \text{ V})$	$8.65 \times 10^{11}$	2.35/2.87 ms	_	49
Optimize morphology and crystallinity (Br, I optimization in Cs <sub>3</sub> Bi <sub>2</sub> I <sub>9-x</sub> Br <sub>x</sub> )	ITO/PEDOT:PSS/ MHP/C <sub>60</sub> /BCP/Ag	$3.5 \times 10^{-9} \text{ A cm}^{-2} (0 \text{ V})$	$4.6 \times 10^{11}$ (410 nm)	40.7/27.1 ms	_	45
Reduce bulk defects (FA incorporated into MAPbI <sub>3</sub> )	ITO/PTAA/MHP/C <sub>60</sub> / BCP/Cu	0.02 pA $Hz^{-1/2}$ (noise signal) <sup>a</sup> (0 V)	27.7 nGy <sub>air</sub> s <sup>-1</sup> (detection limit) <sup>b</sup>	86/500 μs	_	50
Reduce bulk defects and increase film thickness (Cs, DMA optimization in Cs <sub>v</sub> DMA <sub>1-x</sub> PbI <sub>3</sub> )	ITO/PTAA/PMMA/ MHP/PCBM/Bphen/ Cu	$6.4 \times 10^{-5} \text{ mA cm}^{-2} (-0.2 \text{ V, about } 10^3 \text{ times reduced})$		558 ns (TPC extracted) <sup>c</sup>	_	43
Optimize morphology, reduce bulk defects (Br, Cl optimization in CsPbBr <sub>x</sub> Cl <sub>3-x</sub> )	ITO/MHP/Au	$10^{-8} \text{ A cm}^{-2} (0 \text{ V})$	10 <sup>12</sup>	75/70 μs	137	51
Alleviate stress and reduce bulk defects (Cs, MA, FA and Br, I optimization in MHPs)	Au/BCP/C <sub>60</sub> /MHP/ SpiroTTB/Au	$-1.44 \ \mu A \ cm^{-2} \ (-75 \ V)$	42 nGy <sub>air</sub> s <sup>-1</sup> (detection limit) <sup>b</sup>	2.3/57.2 μs	_	41
Optimize morphology (FA, and Sn optimization in MHPs)	ITO/PEDOT:PSS/ MHP/C <sub>60</sub> /BCP/Ag	$5.2 \times 10^{-8} \text{ A cm}^{-2} (-0.2 \text{ V})$		6.9/9.1 μs	167	52
Optimize morphology and reduce bulk defects (Br, I optimization in MAPbBr <sub>3-<math>x</math></sub> I <sub><math>x</math></sub> )	ITO/MeO-2PACz/	$1.3 \times 10^{-9} \ A \ cm^{-2}$ (-0.5 V, about 20 times reduced)	$8.7 \times 10^{12}$	0.58/0.17 μs	133	42

<sup>&</sup>lt;sup>a</sup> Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various frequencies. <sup>b</sup> Detection limit: the detection limit in X-ray detection is defined as the equivalent dose rate to produce a photocurrent greater than three times the noise current (dark current). <sup>c</sup> TPC extracted: speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurrent curves.

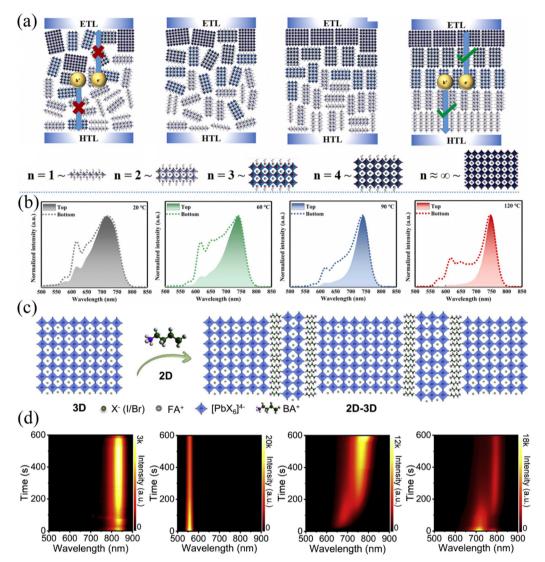


Fig. 7 (a) Schematic diagram of the internal phase arrangement process and the corresponding charge transportation in MHP thin films. (b) The top and bottom PL spectra of different phase arrangement films. Reproduced with permission. 56 Copyright 2023, Elsevier. (c) Schematic illustration of the selfassembled 2D-3D MHPs obtained by an ion-exchange-induced crystallization method. (d) PL spectra monitoring of different 2D-3D MHP combinations.<sup>57</sup> Reproduced with permission. Copyright 2022, Elsevier.

PL spectra monitoring helped unveil the effect of halide anions (Br and I on crystal formation in these thick MHP films (Fig. 7d). The resulting 2D-3D MHP thick film-based devices exhibited extremely low  $J_d$  (0.8 nA cm<sup>-2</sup>), an ultra-fast speed of 640 ns, and a detection limit of 4.2 nGy<sub>air</sub> s<sup>-1</sup>. Furthermore, they demonstrated a prototype 1024-pixel detector array for Xray imaging. The strategies and the corresponding device structures and performance parameters are summarized in Table 2. These advancements in engineering the dimensional and phase distribution of MHPs hold great promise for achieving high-performance and stable MHPPDs.

## 5.3 Additive engineering and the modulation of crystallization methods

Being an ionic crystal, the occurrence of anion/cation vacancies within the bulk and at the interface of MHPs is inevitable

during the thin film formation process. To address this, a passivation technique involving the addition of additives in the bulk and at the interface of MHPs has been developed. This technique creates coordinating bonding, eliminates vacancies, and fills interstitial spaces, ultimately leading to a reduction in  $J_{\rm d}$  of the MHPPDs. We have summarized the progress in MHPPDs achieved through the application of relevant additive engineering for both the bulk and interface of MHPs in Table 3.

For instance, Wang et al. devised a moisture-triggered additive, poly(vinyl alcohol) (PVA), to passivate surface defects in FAPbI<sub>3</sub>. 104 Their results demonstrate that the PVA organic framework fills the grain boundaries of FAPbI3, thereby stabilizing the favorable black phase of FAPbI<sub>3</sub> and guarding against moisture intrusion through strong interactions with water molecules. The PVA-passivated FAPbI3 films also exhibit self-healing capabilities upon bending, activated by water

Table 2 Summary of the dimensional engineering in MHPs for suppressing  $J_d$  and enhancing the FOMs of MHPPDs

Strategy	Device structure	Dark current (density) ( $I_{ m d}$ or $J_{ m d}$ )	D* (Jones)	Speed [rise time $(t_r)$ /fall (decay) time $(t_f)$ ]	LDR (dB)	Ref.
Regulate band alignment (quasi 2D (BDA <sub>0.7</sub> (BA <sub>2</sub> ) <sub>0.3</sub> )(EA) <sub>2</sub> Pb <sub>3</sub> Br <sub>10</sub> MHPs)	ITO/bl-TiO <sub>2</sub> /mp- TiO <sub>2</sub> /MHPs/ PTAA/Au	$2.65 \times 10^{-12} \text{ A (0 V)}$	$2.5\times10^{15}$	270/920 μs	_	58
Regulate band alignment (2D/3D (BzA) <sub>2</sub> - $MA_{n-2}Pb_nI_{3n+1}/MAPbI_3$ )		$8.32 \times 10^{-10}  \text{A cm}^{-2}  (0  \text{V}, \\ \text{about 1.79 times reduced})$	$1.21\times10^{13}$	53/38 μs	_	59
Optimize morphology and reduce bulk defects (quasi 2D $(BA)_2MA_3Pb_4I_{13})$		$2.3 \times 10^{-11} \text{ A cm}^{-2} (0 \text{ V})$	$1.22\times10^{14}$	5.5/4.7 μs	173.4	56
Optimize morphology and crystallinity, reduce bulk defects (quasi 2D $PEA_2MA_4Pb_5I_{16}$ )		0.36 pA $\mathrm{Hz}^{-1/2}$ (noise signal) <sup>c</sup> (0 V)	$1.4\times10^{12}$	64/162 μs	120	60
Regulate band alignment (quasi 2D (BA) <sub>2</sub> MA <sub>4</sub> Pb <sub>5</sub> I <sub>16</sub> )		$5\times10^{-9}~\text{mA cm}^{-2}$ (0 V)	$7 \times 10^{12}$ (600 nm)	1.48/1.58 μs	> 200	61
Regulate band alignment (quasi 2D $(PEA)_2(MA)_{59}Pb_{60}I_{181})$		$1.76 \times 10^{-7} \text{ A cm}^{-2} (0 \text{ V})$	$2.20 \times 10^{12}$ (750 nm)	1.59/0.02 s	41	62
Reduce surface defects and increase crystallinity (2D/3D/2D PEAI/Cs $_{0.05}$ MA $_{0.45}$ FA $_{0.5}$ Pb $_{0.5}$ Sn $_{0.5}$ I $_3$ / PEAI)	ITO/PTAA/PEAI/ MHP/PEAI/C <sub>60</sub> / BCP/Cu	$1.25 \times 10^{-3} \text{ mA cm}^{-2} (-0.1 \text{ V})$	$2.07 \times 10^{11}$ (910 nm)	35 ns TPC extracted <sup>a</sup>	_	54
Alleviate stress and reduce bulk and interface defects (2D/3D (PTABr and PEABr)/tri-cation MHPs)	ITO/PEDOT:PSS/ MHP/PCBM/Ag	_	10 <sup>12</sup> (730 nm)	40 μs TPC extracted <sup>a</sup>	_	53
Optimize morphology and crystallinity (quasi 2D $(BA)_2MA_{n-2}Pb_nI_{3n+1}$ )	ITO/PTAA/MHP/ C <sub>60</sub> /BCP/Au	$10^{-5} \text{ mA cm}^{-2} (3 \text{ kV cm}^{-1})$	_	_	-	63
Optimize morphology and crystallinity (2D-3D (BA <sub>2</sub> PbBr <sub>4</sub> ) <sub>0.5</sub> FAPbI <sub>3</sub> )	ITO/NiO <sub>x</sub> /PEIE/ MHP/C <sub>70</sub> /BCP/ Au	$0.8 \text{ nA cm}^{-2}$	4.2 nGy air s <sup>-1</sup> (detection limit) <sup><math>b</math></sup>	640 ns/—	_	57
Regulate band alignment, optimize morphology and crystallinity and reduce surface defects (2D/3D PEAI/MAPbI <sub>3</sub> )	ITO/SnO <sub>2</sub> /MHP/ PTAA/Au	$\sim 3.1 \times 10^{-14} \text{ A Hz}^{-1/2}$ (noise signal) <sup>c</sup> (0 V, about 1.8 times reduced)		1.7/9.8 μs	161	55
Optimize $G_{3}^{(1)}$ Optimize $G_{3}^{(2)}$	ITO/PTAA/PEIE/ MHP/C <sub>60</sub> /BCP/ Cu	7 fA Hz <sup>-1/2</sup> (noise signal) <sup>c</sup> (-0.5 V)	$3.7 \times 10^{13}$	<80 ns	182	64
Optimize morphology and reduce bulk and surface defects (quasi 2D $PEA_2MA_8Pb_9I_{28}$ )		$1.8  imes 10^{-2} \ \mathrm{pA} \ \mathrm{cm}^{-1} \ \mathrm{s}^{-1} \ \mathrm{V}^{-1} \ \mathrm{(drifting)}^d$	69 nGy <sub>air</sub> s <sup>-1</sup> (detection limit) <sup>b</sup>	_	_	65
Reduce surface defects (2D/3D $PEA_2PbBr_4/MAPbI_3$ )	ITO/MHP/Au	$\begin{array}{c} 2.6 \times 10^{-10} \ A \ cm^{-2} \\ (0.5 \ V \ mm^{-1}) \end{array}$	10.17 nGy <sub>air</sub> s <sup>-1</sup> (detection limit) <sup>b</sup>	228/197 μs	_	66
Reduce surface defects (2D/3D BAI/MAPbI <sub>3</sub> )	ITO/NiO <sub>x</sub> /MHP/ PCBM/Bphen/Ag	$3.78 \times 10^{-10} \text{ A cm}^{-2} (-0.1 \text{ V})$	$1.46 \times 10^{12}$	1.03/3.20 μs	_	27
Regulate band alignment (quasi 2D $(PEA)_2MA_3Pb_4I_{13}$ )	ITO/MHP/ PCBM/Ag	0.4 nA (0 V)	$3.38 \times 10^{12}$ (570 nm)	$20.8/20.6~\mu s$	99.6	67

<sup>&</sup>lt;sup>a</sup> TPC extracted: speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurrent curves. <sup>b</sup> Detection limit: the detection limit in X-ray detection is defined as the equivalent dose rate to produce a photocurrent greater than three times the noise current (dark current). <sup>c</sup> Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various frequencies. <sup>d</sup> Drifting: drifting means the dark current drift period D.

molecules (Fig. 8a). Ionic liquids serve as promising candidates for bulk defect passivation in MHPs due to their diverse controllable sources of anions and cations. Gao et al. showcased the effectiveness of 1-butyl-2,3-dimethylimidazolium chloride (BMIMCl) in passivating defects within CsSnI<sub>3</sub> NWbased films. 95 Their study revealed that BMIMCl exerts a potent passivating effect on Sn-related defects through the large  $\pi$ bonds in N-C=N, enhancing electron density around Sn<sup>2+</sup> in CsSnI<sub>3</sub> and shielding it from oxidation to Sn<sup>4+</sup>. By combining polymethyl methacrylate (PMMA) for bulk defect passivation in CsSnI<sub>3</sub> NW-based films, the CsSnI<sub>3</sub>-based MHPPDs demonstrated reduced  $J_d$  and highly stable behavior (Fig. 8b).

Thiocyanate salts are recognized as effective additives for controlling the crystallization process and delaying oxidation through strong interactions with metal cations. Liu and colleagues investigated the impact of multifunctional tin thiocyanate (Sn(SCN)<sub>2</sub>) additives on Sn-Pb MHPs. 100 Their addition of the additive to the Sn-Pb MHP precursor led to a preferred doublesided surface distribution within the MHP film, effectively reducing Sn oxidation levels (Fig. 8c). Subsequently, they achieved a high  $D^*$  (8.48  $\times$  10<sup>12</sup> Jones at 910 nm) and outstanding stability (lifetime of 2300 h) in NIR MHPPDs. Effective additives in the bulk of quasi-2D MHPs can regulate the 3D MHP phase within quasi-2D MHP films. Di et al. introduced

 Table 3
 Summary of additive engineering and the modulation of crystallization methods for bulk and interface of MHPs to suppress  $J_d$  and enhance FOMs of MHPPDs

Strategy	Device structure	Dark current (density) $(I_{\rm d} \ { m or} \ J_{ m d})$	$D^*$ (Jones)	Speed [rise time $(t_t)$ / fall (decay) time $(t_t)$ ]	LDR (dB)	Ref.
Optimize morphology and crystallinity (Mn doped into	ITO/SnO <sub>2</sub> /MHP/Ag	1	$3.46 \times 10^{10} (405 \text{ nm}) 3.4/2.0 \ \mu s$	3.4/2.0 µs	130.5	89
Optimize morphology, crystallinity and reduce bulk defects	ITO/PEDOT:PSS/MHP/PCBM/	I	$1.15\times 10^{12}$	1.5/21 µs	I	69
(Cs gopen into Fa <sub>0,75</sub> Ma <sub>0,25</sub> Pu <sub>3,5</sub> ) Reduce bulk defects (Cl doped into MAPbI <sub>3</sub> )	BCF/AI ITO/PEDOT:PSS/MHP/C <sub>60</sub> / RCD/C::	$8.4 \times 10^{-8} \mathrm{Acm^{-2}} \left(-0.1\mathrm{V,about112.71 imes} \right)$	$2.71\times10^{12}$		104	20
Optimize morphology (spray-coated CsPbBr <sub>3</sub> quantum dots)	ECF/Cu FTO/TiO <sub>2</sub> /MHP/Spiro- OMeTAD/A11	times reduced) $4 \times 10^{-4} \text{ mA (0 V, about 20 times reduced)}$	$1 \times 10^{14}  (365 \; \mathrm{nm})$	I	06	71
Optimize morphology and crystallinity, and reduce bulk and El surface defects (room-temperature crystallization for Sn–Pb M	Electrode/MoO <sub>3</sub> /PEDOT:PSS/ MHP/PCBM/ZrAcac/Electrode	$(2.8 \pm 0.81) \times 10^{-7}  \mathrm{A  cm^{-2}}  (0  \mathrm{V})$	$10^{11}$	90 ns/2.27 µs	100	72
Optimize morphology and crystallinity (thick FAPbI3	ITO/Poly-TPD/CsI/MHP/C <sub>70</sub> /	I		60 ns (TPC	I	73
Juncuous) Juncuous) Juncuous and Service defects (MAPbI3 and MAPbBr3 thin- ITO/PTAA/MHP/C <sub>60</sub> /BCP/Cu	BCF/Cu · ITO/PTAA/MHP/C <sub>60</sub> /BCP/Cu	1–2 fA $\mathrm{Hz}^{-1/2}$ (noise signal) <sup>a</sup>	$1.5\times 10^{13}~(532~\text{nm})$	4 ns (TPC extracted) <sup><math>b</math></sup> 256	256	74
Single-citystals) Optimize monology and crystallinity, and reduce bulk	FTO/compact TiO <sub>2</sub> /MHP/	$9.71 \times 10^{-6} \mathrm{A \ cm^{-2}} (0 \mathrm{V, \ about \ 4.5})$	$2.46\times10^{11}$	22.4/25.7 µs	I	75
uerects (Agi additive iii CSF Dibig) Regulate band alignment and reduce surface defects (P3HT additive in CSSMR.)	JPUO-CMCTAD/AU ITO/ZnO/MHP/CuSCN/Ag	$10^{-10} \mathrm{A}$	$1.40 \times 10^{14} (532 \text{ nm}) \ 195.2/165.8 \text{ ms}$	195.2/165.8 ms	115	92
Reduce surface defects (thioacetamide (TAA) as an interface TO/SnO <sub>2</sub> /MHP/TAA/Spiro-	ITO/SnO <sub>2</sub> /MHP/TAA/Spiro-	$3.13 \text{ nA cm}^{-2} (0 \text{ V})$	$8.39\times10^{12}$	1.05/5.04 µs	118	77
material on CsPoBf3) Reduce surface defects and regulate band alignment (rubrene ITO/ZnO/MHP/rubrene/Au	OMETAD/Ag : ITO/ZnO/MHP/rubrene/Au	$1.04\times10^{-10}~\mathrm{A}$	$2.61\times10^{13}$	79.4/207.6 µs	I	78
as an interface material on CSFDD13/ (Reduce crystalline temperature and optimize morphology (ionic liquid Lbutyl-2,3-dimethylimidazolium chloride additions)	FTO/SnO <sub>2</sub> /MHP/carbon	5 nA	$1.87\times 10^{12}$	0.24/0.29 ms	100	79
LIVE III CS2Ag DDB.6.) Reduce bulk and surface defects (3-(1-pyridinio)-1-propanesulfonate (PPS) for the buried layer and the additive for MHD)	ITO/SnO <sub>2</sub> /PPS/MHP:PPS/Ag	$6.05 \times 10^{-11} \text{ A (about 2 times reduced)}$	$1.51\times 10^{13}$	0.74/0.09 s	I	80
Regulate band alignment and optimize crystallinity (NH <sub>4</sub> Cl additional DMCC solvent for (DEA) MA DE 1	ITO/PEDOT:PSS/MHP/PCBM/	$1.7 \times 10^{-4} \text{ mA cm}^{-2} \text{ (about 2 times } 6 \times 10^{11} \text{ (600 nm)}$	$6 \times 10^{11}  (600 \; \mathrm{nm})$	5.8/4.6 ms	126	81
audutive and Divisor Solvent for (T.E.A)2M1433 Regulate band alignment and reduce surface and bulk defects ITO/MHP/PCBM/Ag (Ascharacide (CBH) of an Additive for (DRA) MA Dk 1 )	ppileti/At ; ITO/MHP/PCBM/Ag	.— —	$1.31 \times 10^{12} \ (570 \ \mathrm{nm})$	0.532/0.521 ms	I	82
Reduce surface defects (4-amino-2,3,5,6-tetrafluorobenzoic	ITO/PTAA/MHP/C <sub>60</sub> /BCP/Cu	$1.2 \times 10^{-5} \text{ mA cm}^{-2} (-0.1 \text{ V, about 5.34})$	$5.34 \times 10^{12} \text{ (850 nm)}$		224	83
acid (AIFBA) as an additive for $CS_{0.15}FA_{0.85}PD_{0.5}N_{0.543}$ ) Optimize morphology and crystallinity (3,3,4,4-benzophenonetetracarboxylic dianhydride (BPTCD) as an additive for MAPPL.)	ITO/PEDOT:PSS/MHP/PCBM/ Ag	10 times reduced) $9.98 \times 10^{-8} \text{ A } (-0.5 \text{ V, about } 29 \text{ times reduced})$	$4.55\times 10^{11} (685\; nm)$	extracted)* 850/800 ms	I	84
organization of the property o	ITO/NiOx/MHP/PCBM/BCP/Ag		$7.28\times10^{12}$	5/18 µs	I	85
additive for MAPbl <sub>3</sub> )  Reduce surface and bulk defects (trimethylolpropane triacry- ITO/MHP/Au	· ITO/MHP/Au	times reduced) 2.35 × $10^{-14}$ A Hz <sup>-1/2</sup> (noise signal) <sup>a</sup>	67 nGy s <sup>-1</sup> (detection	I	I	98
iate (1M1A) crossilined MAPD13) Optimize morphology and crystallinity (1-butyl-3-methylimidazolium bromide (BMIMBr) as an additive for Cepher.	ITO/SnO <sub>2</sub> /MHP/Carbon	o.s ta cm s v (armung) $2.51 \times 10^{-10} \mathrm{A}(0\mathrm{V})$		0.06/0.26 ms	140	87
Regulate band alignment and optimize crystallinity (NH <sub>4</sub> SCN IT	I ITO/NiO <sub>x</sub> /MHP/PCBM/ZnO/Ag	2.43 nA cm $^{-2}$ (0 V, about 28 times	$2.46 \times 10^{12} (610 \text{ nm}) 42.8/135.2 \text{ ns}$	42.8/135.2 ns	111.4	88
Reduce bulk and surface defects (ascorbic acid (AA) as an antioxidant additive for MA <sub>0.5</sub> FA <sub>0.5</sub> PA <sub>0.5</sub> Sn <sub>0.5</sub> S <sub>3</sub>	$\begin{array}{l} TTO/PEDOT:PSS/MHP/\\ PC_{61}BM/bis-C_{60}/Ag \end{array}$	1.5 pA Hz <sup>-1/2</sup> (noise signal) <sup>a</sup>	$10^{12} (800-1000 \text{ nm})$	7.4 µs	10 <sup>10</sup> (photon	88
Reduce surface defects, optimize morphology and crystallinity (two-step spin-coating method for $MAPb1_3$ )	ITO/PEDOT:PSS/MHP/ PC <sub>61</sub> BM/BCP/Au	5.55 $\times 10^{-4}~\text{mA}~\text{cm}^{-2} \left(-1.5~\text{V, about}~5 \times 10^{11} \left(532~\text{nm}\right)$ 3 times reduced)	$5 \times 10^{11} \ (532 \ \mathrm{nm})$	2.6/72.8 µs	number) 106	06

Published on 08 2024. Downloaded on 16/10/2025 08:32:40.

Table 3 (continued)

Strategy	Device structure	Dark current (density) $(I_d \text{ or } I_d)$	$D^*$ (Iones)	Speed [rise time $(t_r)$ / fall (decay) time $(t_i)$ ] LDR (dB)	LDR (dB)	Ref.
Reduce surface defects (thiophene-2-carbohydrazide (TAH), TTO/PEDOT:PSS/MHP/	ITO/PEDOT:PSS/MHP/	$1.5 \times 10^{-8} \text{ mA cm}^{-2} (-0.07 \text{ V})$	$1.8 \times 10^{12} $ (840 nm)	94/97 ns	,	91
an antioxidant additive for $FA_0.7MA_{0.3}PD_{0.5}Sn_{0.5}J_3$ Reduce bulk and surface defects (an urea additive for MAPbI <sub>3</sub>	PC <sub>61</sub> BM/C <sub>60</sub> /BCP/Ag ITO/NiO <sub>x</sub> /MHP/PCBM/BCP/Ag	$1.82  imes 10^{-11}  ext{ mA cm}^{-2}$	$2.5 \times 10^{-2} (940 \text{ nm})$ $1.42 \times 10^{14}$	I	162	92
Optimize crystallinity and reduce surface defects (tetra- $ TO $ PTAA/PEIE/MHP/ $C_{70}$ / $7.7  imes 10^{-10}$ A cm $^{-2}$ $(-0.2 \text{ V})$	ITO/PTAA/PEIE/MHP/C <sub>70</sub> /	$7.7  imes 10^{-10}  ext{ A cm}^{-2} (-0.2  ext{ V})$	$10^{12}$	188/630 ns	132	93
fluoroborate and hexafluorophosphate additives for FAPbI <sub>3</sub> ) BCP/Cu Optimize morphology and crystallinity, and reduce bulk and FTO/SnC	BCP/Cu FTO/SnO <sub>2</sub> /MHP/P3HT/Ag	$2.2 \times 10^{-10} \text{ mA cm}^{-2} (0 \text{ V}. 10^4 \text{ times } 1.69 \times 10^{13}$	$1.69 \times 10^{13}$	23.5/21.2 ms	41.93	94
surface defects (fluorinated aminobenzoic acid isomers [3-		reduced)				
amino-2,6-difluorobenzoic acid (13-FABA) and 4-amino-3,5-difluorohenzoic acid (14-FABA)] as additives for CephBr.						
Reduce bulk and surface defects (1-butyl-2,3-	ITO/SnO <sub>2</sub> /MHP/Carbon	$2 imes 10^{-11}\mathrm{A}$	$1.18\times 10^{12}$	0.23/0.19 ms	180	95
dimethylimidazolium chloride (BMIMCI) and PMMA as	1					
definition of the company and crystallinity (AgI as an additive for ITO/PTAA/PEIE/MHP/PC <sub>60</sub> BM/	ITO/PTAA/PEIE/MHP/PC60BM/	1	$3.5 \text{ nGy s}^{-1} \text{ (detec-}$	280/450 ns	I	96
$CsSnI_3$ )	C <sub>70</sub> /BCP/Cu		tion $\lim_{\epsilon \to 0} f$			
Optimize morphology and reduce surface defects (excess	ITO/PEDOT:PSS/MHP/	$3.46 \times 10^{-4} \text{ mA } (-1 \text{ V, about } 2$	$3.38 \times 10^{12} (532 \text{ nm}) 5.90/6.75 \text{ µs}$	5.90/6.75 µs	80	26
PMMA as an additive for MAPbI <sub>3</sub> )	$PC_{61}BM/Au$	times reduced)				
Optimize morphology and reduce bulk and surface defects	ITO/SnO <sub>2</sub> /MHP/PTAA/MoO <sub>3</sub> /	$4.40 \times 10^{-8} \mathrm{A~cm}^{-2} (\mathrm{about~778}$	$1.9 \times 10^{11} (532 \text{ nm}) 0.03 \text{ ms}$	0.03 ms	119	86
(poly(ethylene glycol) (PEG) additives for CsPbI <sub>2</sub> Br)	Ag	times reduced) $(-0.1 \text{ V})$	;			
Optimize morphology and crystallinity, reduce surface defects ITO/SnO <sub>2</sub> /MHP/Spiro-	ITO/SnO <sub>2</sub> /MHP/Spiro-	$1.53 \times 10^{-9} \text{ A cm}^{-2} (0 \text{ V, about 8})$	$7.74 \times 10^{12} (450 \text{ nm}) \ 0.155/0.155$	0.155/0.155 s		66
(PMMA/sodium borate salt (Borax) as interface materials for OMeTAD/Ag	OMeTAD/Ag	times reduced)				
$C_{S_{0.05}FA_{0.6}MA_{0.35}Pb(Br_{0.6}Cl_{0.4})_3)}$			10, 212, 64.5	9	0	
Optimize morphology and crystallinity, reduce surface detects 110/PEDOT:PSS/MHP/MHP/	ITO/PEDOT:PSS/MHP/MHP/	$9.85 \times 10^{-2} \text{ A cm}^{-2} (-0.4 \text{ V, about } 8.48 \times 10^{-2} (910 \text{ nm}) 67.5 \text{ ns/0.72 } \mu\text{s}$	$8.48 \times 10^{-2} (910 \text{ nm})$	67.5 ns/0.72 μs	213	100
(tin thiocyanate additive for FA <sub>0.85</sub> CS <sub>0.15</sub> Sn <sub>0.5</sub> Pb <sub>0.5</sub> I <sub>3</sub> )		60 times reduced)	Ç			
Optimize morphology and reduce surface defects (MAPbI <sub>3</sub> /		$5.7 \times 10^{-7}$ mA (0 V, about 2 times $1.07 \times 10^{-2}$	$1.07\times 10^{12}$	50/17 µs	127	101
PMMA)	BCP/Al	reduced)	7			
Reduce surface defects (3,4,5-tris (n-dodecyloxy) benzoyla-	ITO/PTAA/MHP/TBA-Azo/C <sub>60</sub> /	$9.61 \times 10^{-3}  \mathrm{mA  cm^{-2}} (-0.1  \mathrm{V, about  2.21} \times 10^{11} (758  \mathrm{nm})  42.9  \mathrm{ns}  (\mathrm{TPC})$	$t \; 2.21 \times 10^{11} \; (758 \; \mathrm{nm})$	$42.9 \text{ ns} \left( \text{TPC} \right)$	185	102
mide with an azobenzene moiety (TBA-Azo) additives for Sn– BCP/ Pb MHP)	BCP/Cu	100 times reduced)		extracted)"		
Optimize morphology, reduce surface defects (PMMA as a	ITO/NiO <sub>x</sub> /PMMA/MHP/	$4.0 \times 10^{-7} \text{ mA cm}^{-2} (0 \text{ V, about } 2 1.28 \times 10^{12})$	$1.28\times 10^{12}$	57/18 µs	139	103
double-sided passivation layer)	PMMA/PCBM/ZnO/BCP/Al	times reduced)				

<sup>&</sup>lt;sup>a</sup> Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various frequencies. <sup>b</sup> TPC extracted: speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurrent curves. <sup>c</sup> Detection limit: the detection limit in X-ray detection is defined as the equivalent dose rate to produce a photocurrent greater than three times the noise current).

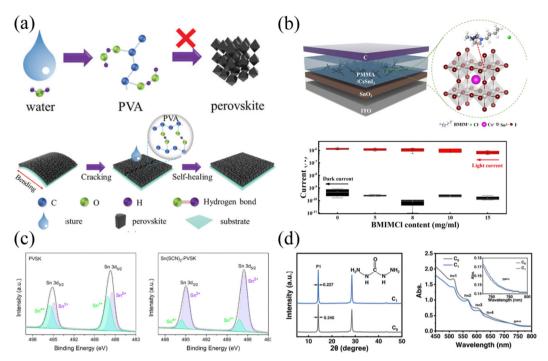


Fig. 8 (a) The mechanism of protection and self-healing process by PVA in FAPbl<sub>3</sub> films. Reproduced with permission. <sup>104</sup> Copyright 2021, Wiley-VCH. (b) MHPPD based on the CsSnI<sub>3</sub> with BMIMCl additive and photo/dark current. Reproduced with permission. <sup>95</sup> Copyright 2022, Nature. (c) Sn 3d XPS spectra of the pure Sn-Pb and Sn(SCN)<sub>2</sub> Sn-Pb films. Reproduced with permission. <sup>100</sup> Copyright 2023, ACS. (d) XRD patterns and UV-vis absorption spectra of the control and with CBH quasi-2D MHP films. Reproduced with permission. 82 Copyright 2023, Wiley-VCH.

carbohydrazide (CBH) additives into quasi-2D (PEA)2MA3Pb4I13 precursors, resulting in significantly improved crystallinity and alignment of the 3D phase. 82 This enhancement was evident in sharper XRD diffraction peaks and a higher ratio of the 3D MHP phase in quasi-2D MHP films, impacting their absorption characteristics (Fig. 8d).

In addition to incorporating additives in the bulk and at the interface of MHPs to passivate defects and regulate phase distribution, researchers have explored modifications to fabrication and crystallization methods to achieve the same objectives. For instance, Bao and colleagues synthesized thin single crystals of MHPs using space confinement methods to significantly reduce bulk defect density and eliminate grain boundaries in polycrystalline MHPs.74 As depicted in Fig. 9a and b, the synthesized thin single crystals of MAPbBr<sub>3</sub> and MAPbI<sub>3</sub> exhibited excellent X-ray diffraction patterns with [100] orientation growth, and thermal admittance spectroscopy revealed a low trap state density. The resulting MHPPDs based on these thin single crystals demonstrated low noise currents of 1-2 fA Hz<sup>1/2</sup> and ultra-low sub-pW cm<sup>-2</sup> weak light detection limits. In a separate study, Zhu and colleagues introduced room-temperature crystallization in a Sn-rich binary MHP system to achieve compact and smooth Sn-Pb MHP thin films.<sup>72</sup> By utilizing the strong Sn-O ionic bond between SnI<sub>2</sub> and dimethyl sulfoxide (DMSO), as well as the Sn-I ionic bonding between MAI and SnI<sub>2</sub>, the Sn-rich binary MHP precursor films could crystallize at room temperature and transform into black and smooth films after antisolvent treatment and the annealing process (Fig. 9c). These resulting thin films

were successfully demonstrated on metal-oxide-semiconductor substrates, and the MHPPDs based on this method exhibited a large LDR of 100 dB and a fast speed of 2.27 µs. Wang and colleagues developed a modified two-step spin-coating method for producing large grain size and pinhole-free Pb-based MHP thin films. 90 In the modified step, MAI was intercalated with PbI<sub>2</sub> on the surface to form an intermediate phase, which was then transformed into the desired polycrystalline MHP film after thermal annealing (Fig. 9d). By optimizing the concentration of MAI in the MAI:PbI2 mixture, the target thin film could be achieved (Fig. 9e). The resulting P-I-N MHPPDs based on this MHP thin film exhibited the lowest  $I_d$  of 5.55  $\times$  $10^{-4}$  mA cm<sup>-2</sup>, as well as a fast speed of 2.6  $\mu$ s and 72.8  $\mu$ s. Furthermore, researchers have also minimized bulk defects in MHPs through the fabrication of thick MHP films using thermal evaporation methods<sup>73</sup> and the production of MHP QD films through spray-coating methods.<sup>71</sup>

## 5.4 Engineering of the MHP/CTL interfaces

It is important to note that shallow-energy defects can transform into deep traps in MHP films, leading to performance degradation and instability in devices. Near the surface of MHPs, the density of deep traps is significantly higher, ranging from one to two orders of magnitude greater than in the bulk. Surface defects in MHPs, including A-site, B-site, and X-site vacancies, as well as B-site antisite substitutions, are primarily responsible for the presence of surface or buried defect states. These states contribute to detrimental leakage current and the rapid degradation of MHPPDs. Moreover, the energy level

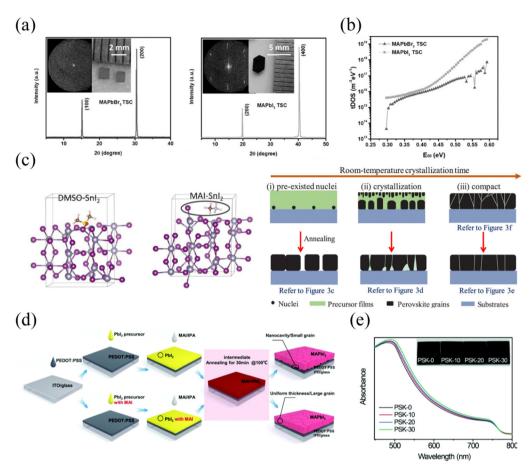


Fig. 9 (a) XRD patterns of MAPbBr<sub>3</sub> and b) MAPbI<sub>3</sub> single-crystals obtained from the 2D X-ray diffraction patterns. Insets are the 2D X-ray diffraction patterns along with the photographs of the single crystals. (b) Trap-density-of-states curves of devices based on MAPbBr<sub>3</sub> and MAPbI<sub>3</sub> single-crystals. Reproduced with permission.<sup>74</sup> Copyright 2017, Wiley-VCH. (c) Schematic illustrations of the bonding between Snl<sub>2</sub> and DMSO, and the bonding between SnI<sub>2</sub> and MAI, along with the crystallization process of the Sn-Pb films. Reproduced with permission.<sup>72</sup> Copyright 2019, ACS. (d) Modified twostep spin-coating method for producing high-quality MAPbI<sub>3</sub> films. (e) Absorption curves and optical images of the various MAI concentrations are conducted in the second step. Reproduced with permission.<sup>90</sup> Copyright 2022, RSC.

alignment and charge extraction at the interface play a crucial role in determining the device's overall performance. Therefore, effective interface engineering between MHPs and CTLs is crucial for passivating these defects and establishing a cascade architecture, ultimately reducing  $J_d$  in MHPPDs.

The importance of interface engineering in MHPPDs differs from that in photovoltaic devices based on MHPs with a common structure involving a mesoporous oxide/MHP heterojunction or a planar architecture utilizing thin CTLs. In MHPbased photovoltaics, the large effective junction area results in a substantial parasitic capacitance, leading to slow speed and current leakage due to the presence of large crystallites in the thin film. To address this issue, Lin and colleagues achieved high-performance MHPPDs by incorporating relatively thick double fullerene hole blocking layers (HBLs) (PC<sub>60</sub>BM/C<sub>60</sub>). This design effectively reduced the shunt capacitance, enabling ultra-fast photo-response and suppressing current leakage by creating a large hole injection barrier. 105 Similarly, Fang et al. employed a cross-linked hole-transporting layer, N4,N4'-bis(4-(6-((3-ethyloxetan-3-yl)methoxy)hexyl)phenyl)-N4,N4-diphenylbiphenyl-4,4'-diamine (OTPD) (Fig. 10a), and controlled the thickness

of the  $\rm C_{60}$  layer to suppress  $\it J_{\rm d}$  (9.1  $\times$   $\rm 10^{-9}~A~cm^{-2}$  at  $\rm -2~V)$  and noise current (5.5 fA  $Hz^{-1/2}$  at -0.1 V) in MHPPDs.<sup>10</sup> In another study reported by Bao and co-workers, polyethyleneimine ethoxylate (PEIE) was introduced as a substrate modifier for long-term stable inorganic MHPPDs. This modification resulted in ultra-fast MHPPDs with a speed of 602 ns to 20 ns for CsPbIBr<sub>2</sub> and CsPbBr<sub>3</sub> (Fig. 10b) over various active areas. 106

In addition to organic interface layers, inorganic oxide layers deposited using atomic layer deposition (ALD) show promise for suppressing  $J_d$  and enabling ultra-fast MHPPDs. Cen et al. utilized ALD to fabricate CsPbBr3-based MHPPDs with Al2O3 and TiO2 interfacial layers 107 (Fig. 10c). These layers significantly reduced current leakage by more than three orders of magnitude, leading to the successful realization of robust visible light communication systems. The investigation of organic CTLs for MHPPDs in X-ray detection has also been explored. Demchyshyn and co-workers employed PCBM and PTCDI as the HBL and PEDOT:PSS and  $NiO_x$  as the hole transport layer in a P-I-N MHPPD structure using  $(Cs_{0.05}(FA_{0.83}MA_{0.17})_{0.95}PbI_{3-x}Br_x)$  as the high energy photon absorption layer. 108 The results demonstrated different

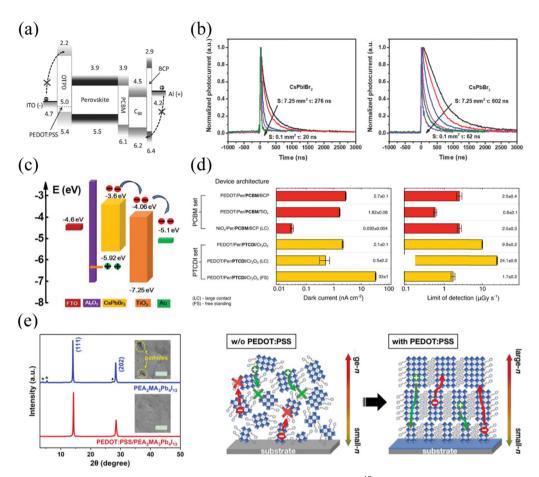


Fig. 10 (a) Energy diagram of the cross-linked OTPD MHPPDs. Reproduced with permission. Oppyright 2015, Wiley-VCH. (b) Transient response curves of the inorganic MHPPDs with PTAA/PEIE. Reproduced with permission. 106 Copyright 2018, Wiley-VCH. (c) Energy band diagram of the MHPPDs with ultrathin Al<sub>2</sub>O<sub>3</sub> and TiO<sub>2</sub> modification layers. Reproduced with permission.<sup>107</sup> Copyright 2019, Wiley-VCH. (d) Summary of the interface engineering based on several organic materials. Reproduced with permission. <sup>108</sup> Copyright 2020, Wiley-VCH. (e) XRD patterns of quasi-2D thin films without and with PEDOT:PSS interlayer (left), the insets are the corresponding top-view FESEM images (scale bar: 1 μm), and schematic illustration of the orientational growth of MHP films without/with PEDOT:PSS interlayer. Reproduced with permission. 109 Copyright 2023, Wiley-VCH.

performance characteristics for different configurations, with the lowest  $J_{\rm d}$  (0.030  $\pm$  0.004 nA cm<sup>-2</sup>) achieved in the NiO<sub>x</sub>/ MHP/PCBM/BCP configuration and the lowest detection limit  $(0.58 \pm 0.05 \,\mu\text{Gy s}^{-1})$  in the PEDOT/MHP/PCBM/TiO<sub>x</sub> configuration. (Fig. 10d) Furthermore, Zhang et al. investigated the importance of PEDOT:PSS and PC71BM in quasi-2D PEA2-MA<sub>3</sub>Pb<sub>4</sub>I<sub>13</sub>-based MHPPDs for UV-A region detection. <sup>109</sup> The inclusion of PEDOT:PSS as the substrate enhanced the vertical orientation of PEA2MA3Pb4I13, as indicated by a smoother XRD pattern. (Fig. 10e) The uniform crystalline morphology and gradient phase distribution of quasi-2D MHPPDs obtained here exhibit a respectable  $D^*$  of 1.3  $\times$  10<sup>12</sup> Jones, along with a swift speed of 313 µs/40.8 ms. Furthermore, extensive efforts have been directed towards introducing new CTLs and modifying both organic and inorganic CTLs to effectively passivate surface defects, construct cascades, and suppress  $J_d$ , thereby enhancing the performance of MHPPDs, as outlined in Table 4.

#### 5.5 Heterojunctions

Forming heterojunctions with MHPs, either by using MHPs themselves or other semiconductors with superior optoelectronic properties, offers significant advantages. These heterojunctions suppress unwanted current leakage by constructing P-N junctions and enhance device performance in several ways. They expand the photoresponse range by incorporating additional photoresponsive materials and improve stability by protecting the MHPs. Zhang et al. demonstrated a solution-based epitaxial method for the controlled fabrication of MHP single crystal heterojunctions, including MAPbBr<sub>3</sub>/ MAPbI<sub>3</sub> and MAPbCl<sub>3</sub>/MAPbBr<sub>3</sub> heterojunctions. 148 The epitaxial growth process is illustrated in Fig. 11a. By analyzing the PL properties of different locations along the cross-section of the MHP single crystal heterojunction, the researchers confirmed the controllable gradual conversion from p-type (MAPbI<sub>3</sub>) to ntype (MAPbBr<sub>3</sub>) characteristics (Fig. 11b). The high-quality MHP single crystal heterojunctions with a gradient energy band structure at the heterointerface (Fig. 11b) enabled the optimized MHPPDs to achieve low detection limits for direct X-ray detection and minimal  $J_d$  drift. Likewise, Liu and colleagues employed an epitaxial method through vapor-phase deposition to establish a monocrystalline CsPbBr<sub>3</sub> (p-type)-SrTiO<sub>3</sub> (n-type) halide-oxide perovskite P-N heterojunction, as depicted in

Published on 08 2024. Downloaded on 16/10/2025 08:32:40.

**Table 4** Summary of the engineering of the MHP/CTL interfaces for suppressing  $J_d$  and enhancing the FOMs of MHPPDs

Strategy	Device structure	Dark current (density) ( $I_{ m d}$ or $J_{ m d}$ )	$D^*$ (Jones)	Speed [rise time $(t_r)$ / fall (decay) time $(t_t)$ ]	LDR (dB)	Ref.
Reduce surface defects and regulate band alignment (silane TTO) barrier-capped MAPbBr <sub>3</sub> quantum dots as an HBL) capp	ITO/PEDOT:PSS/MHP/silane barrier- capped MAPbBr <sub>3</sub> quantum dot/PC <sub>70</sub> BM/	2.19 $\times$ 10 <sup>-7</sup> A cm <sup>-2</sup> (0 V, about 7.85 $\times$ 10 <sup>12</sup> 2.5 times reduced)	t 7.85 $ imes$ 10 $^{12}$	I		110
Reduce surface defects (3,4,5-tris ( $n$ -dodecyloxy)benzoylamide TTO/PTAA/MHP/TBA-Azo/C <sub>60</sub> /BCP/Cu with an azobenzene moiety (TBA-Azo) additives for Sn-Pb	ng : ITO/PTAA/MHP/TBA-Azo/C <sub>60</sub> /BCP/Cu	$9.61 \times 10^{-5}  \mathrm{mA  cm^{-2}}  (-0.1  \mathrm{V},  2.21 \times 10^{11} $ about 100 times reduced) (758 nm)	, $2.21 \times 10^{11}$ (758 nm)	42.9 ns (TPC extracted) <sup><math>b</math></sup>	185	102
Regulate band alignment, increase optical absorption and reduce surface defects (1 2,2'-(12Z,2'Z)-(15,5'-(4,4,9,9-tetrakis(4-hexylphenyl)-4,9-dihydro-s-indaceno[1,2-b:5,6-b]dithiophene-2,7-diyl)bis(4-((2-ethylhexyl)-oxylthiophene-5,2-diyl)bis(methanylidene))bis(3-oxo-2,3-di-hydro-1 <i>H</i> -indene-2,1-divilana))dixaging (FETO) as a prince-land	TO/PTAA/MHP/IEICO/C <sub>60</sub> /BCP/Cu	$2.6 \times 10^{-5} \ \mathrm{mA \ cm^{-2}} \ (-0.1 \ \mathrm{V}, \ 1.45 \times 10^{12}$ about 1000 times reduced) (650 nm)	(650  nm)	27 ns (TPC extracted) $^b$	198	111
2,1*ujyluetle)julinatolioniune (IECO) as an interlayet Reduce interface defects and form interfacial dipole (bromi- Si/APTES/MHP/C <sub>60</sub> /BCP/Au nated (3-aminopropyl)triethoxysilane (APTES) as an	Si/APTES/MHP/C <sub>60</sub> /BCP/Au	$23 \text{ nA cm}^{-2} (-1 \text{ V})$	9.5 $\mu Gy_{air} s^{-1}$ (detection limit) <sup>c</sup>	—/255 µs	I	112
Regulate band alignment and reduce interface defects	ITO/NiO <sub>x</sub> :PbI <sub>2</sub> /MHP/C <sub>60</sub> /BCP/Ag	$2\times 10^{-10}~{\rm A~cm^{-2}}~(-0.2~{\rm V})$	$10^{13}$	168 ns (TPC	112	113
(NIOx:PO12 handcomposites as an EDL) Regulate band alignment and reduce surface defects (MAPbI <sub>3</sub> / ITO/TAPC/MHP/PBDB—T: IHIC/PC <sub>61</sub> BM/ poly[(2,6-(4,8-bis(5-(2-ethylhexyl)thiophen-2-yl)-benzo[1,2- Ag. b:4,5-b']dithiophene)]-alt-(5,5-(1',3'-di-2-thienyl-5',7'-bis(2-ethylhexyl)benzo[1',2'-c:4',5'-c'] dithiophene-4,8- dione]](PBDB-T):dithienocyclopenta-thieno[3,2-b] thiophene core end-capped with 1,1-dicyano-methylene-3-indanone unit	TTO/TAPC/MHP/PBDB—T: IHIC/PC <sub>61</sub> BM/ Ag.	$1.01 \times 10^{-4}$ mA cm <sup>-2</sup> (-0.05 V, about 4 times reduced)	(600  nm)	extracted)	1	114
(Enc.))  Regulate band alignment and increase optical absorption	ITO/PEDOT:PSS/MHP/PC7,BM/BCP/Ag	$13.7~{ m pA~Hz}^{-1/2}~{ m (noise~signal)}^a$	$\begin{array}{c} 2.61 \times 10^{12} \\ (740 \text{ nm}) \\ 2.57 \times 10^{12} \end{array}$	29.3/11.7 µs	106.8 115	115
(FAPb <sub>0.5</sub> Sn <sub>0.5</sub> I <sub>3</sub> /tin monosulfide quantum dots) Regulate band alignment and suppress electrochemical	Au/Al/BCP/C <sub>60</sub> /MHP/Au	(about 2.5 times reduced) 3 nA (100 V mm <sup>-1</sup> )		7.75/8.79 ms		116
reaction (BCP as an interfacial layer between MHP and Al) Regulate band alignment and reduce interface defects (poly[4- ITO/] (10 <i>H</i> -phenothiazin-10-yl)- <i>N</i> , <i>N</i> -bis(4-methoxyphenyl)aniline]	. ITO/PPZ-TPA/MHP/C <sub>60</sub> /BCP/Cu	$1.26 \times 10^{-7} \text{ A cm}^{-2} (-0.1 \text{ V},$ about 10 times reduced)	(detection limit) <sup>2</sup> .46 $\times$ 10 <sup>11</sup> (730 nm)	$0.18~\mu \mathrm{s}~(\mathrm{TPC}$ extracted) $^b$	I	117
(PPL-1PA) as an EBL)  Negative band alignment and reduce interface defects (Spiro- ITO/SnO <sub>2</sub> /MHP/Spiro-OMeTAD/MoO <sub>3</sub> /Cu	$\cdot  TFO/SnO_2/MHP/Spiro-OMeTAD/MoO_3/Cu$	$9.72\times 10^{-10}~\mathrm{A~cm^{-2}}$	$2.7\times 10^{13}$	54.1/10.7 µs	126	118
nt (PMMA:Au nanocomposites as an	ITO/PEDOT:PSS/MHP/ZnO/PMMA:Au/	(about 1000 times reduced)	$2.7 \times 10^{15} (532 \text{ nm}) 631/452 \text{ ms}$	631/452 ms	I	119
nicitayet) Regulate band alignment (graphene as a transparent conductive departed and MAC of on EDI)	Graphene/MoS <sub>2</sub> /MHP/OCBM/BCP/Al	I	$7.99\times10^{10}$	0.7-0.9/0.4-0.6 s	117	120
uncure erectione and mozy as an EBE   Reduce interface defects and optimize morphology (cross-linked DWR as an EBE)	ITO/cross-linked PVK/MHP/C <sub>60</sub> /BCP/Cu	$5.23 \times 10^{-4} \text{ mA cm}^{-2} (-0.1 \text{ V}, 2.06 \times 10^{11} \text{ shout 2 times raduced})$	$(730 \times 10^{11})$	0.47  ms (TPC	I	121
Regulate band alignment, reduce interface defects and opti- ITO/PEDOT:PSS/Triazine-Th-OMeTAD/	ITO/PEDOT:PSS/Triazine-Th-OMeTAD/	1.09 nA cm <sup>-2</sup> (0 V)	$8.2 imes10^{12}$	$\begin{array}{c} \text{catacted} \\ 18 \text{ ns } (\text{TPC} \\ \text{extracted})^b \end{array}$	166	122
unize morphology (unazine-in-OmerAD) as an EBL) Optimize morphology and crystallinity, and reduce interface ITO/NiO <sub>x</sub> /F4-TCNQ/MHP/BCP/C <sub>60</sub> /Cu	MLP/FCDM/DCF/Pg ITO/NiO <sub>x</sub> /F4-TCNQ/MHP/BCP/C <sub>60</sub> /Cu	1.5 $\times$ 10 <sup>-10</sup> A cm <sup>-2</sup> (0 V, about 7.2 $\times$ 10 <sup>13</sup>	t 7.2 $ imes 10^{13}$	extracted) 68.2/11.6 μs	127.1 123	123
uciects (r**10.NQ*mounted NIO*, Interlayer) Regulate band alignment and reduce interface defects (PED- ITO/PEDOT:PSS/MHP/PC71BM/Ag Cornes on the following continuing the collection)	ITO/PEDOT:PSS/MHP/PC <sub>71</sub> BM/Ag	1.3 dilles reduced) —	$1.3 \times 10^{12}  (330 \; \mathrm{nm}) \; 313 \; \mu \mathrm{s}/40.8 \; \mathrm{ms}$	313 µs/40.8 ms		109
Section 25 as an EDL and the Solvent Optimization) Reduce interface defects and optimize morphology (PMMA incertion between NiO and MHD)	ITO/NiO <sub>x</sub> /PMMA/MHP/PCBM/ZnO/Al	From 5.9 to 5.6 $\times$ 10 <sup>-8</sup> mA	$4.5\times 10^{13}$	52/18 µs	129	124
Regulate band alignment (PFN as an HBL)	ITO/PEDOT:PSS/MHP/PCBM/PFN/Al	$<1 \text{ pA Hz}^{-1/2} \text{ (noise signal)}^a$	$4 \times 10^{14}$	180/160 ns	>100	125

_	
7	3
(	ŭ
•	3
i	≍
	=
4	~
3	_
(	2
(	٥
•	-
5	4
5	٠.
_	π 1
	Ď
7	ge
7 2 2 2	Ď

rnai oi	Ма	teriais	Cne	mis	try (	-																	Rev	view
Ref.	126	127	128	129	130	106	131	132	2 133	134	108	135	136	172.7 107	137	186.7 138	10	139	140	128.6 141	142	105 143	31	144
LDR (dB)	124	132		156	I	200	132	80	135.2	200	1	164	112	172.	118	186.	94		100	128.0	98	230	-	113
Speed [rise time $(t_{ m r})/$ I fall (decay) time $(t_{ m f})]$ (	$5.3 \times 10^{13}  (640  \mathrm{nm})  115.32/11.30 \; \mu \mathrm{s}$	< 0.02 s	0.9/1.8 ms	m) 2.89/1.93 µs	15.7/15.5 µs	m) 20 ns (TPC	extracted)* 460/556 ns	m) 3/6 µs	6.8/5.5 µs	95 ns	I	105.7/106.7 µs	m) 3.0/2.2 μs	28/270 µs	<47/47 ms	0.056/0.25 ms	m) 0.12 $\mu s$ (TPC		a) 500 ns (estimated)	0.57/0.58 ms	m) —	1.7/1.0 $\mu s$ m) 597 $ns(TPC$ extracted) <sup>b</sup>	<sup>.2</sup> 1.2/3.2 µs	
$D^*$ (Jones)	$5.3 \times 10^{13}  (640  \mathrm{n})$	$1.02  imes 10^{13} \ (580  ext{ nm})$	$3.6\times10^{11}$	$2.3 \times 10^{13} (660 \text{ nm}) 2.89/1.93 \ \mu s$	$2.54 \times 10^{11}$		$1.13\times10^{13}$	$J_{1},1.2 imes10^{12}(450~{ m n})$	$s 10^{12}$	$', 10^{13}$	$0.58 \pm 0.05  \mu \mathrm{Gy}$ $\mathrm{s}^{-1}(\mathrm{detection})$		7, 1.1 × $10^{13}$ (532 n	$1.88 \times 10^{13}$	$4.2 \times 10^{12}$	$1.59\times10^{13}$	$7.4  imes 10^{12}  ext{ (680 nm) } 0.12  ext{ µs (TPC)}$	12 $\mu$ Gy s <sup>-1</sup> (detec-	$4 \times 10^{12} (500 \text{ nm})$	$3.39 \times 10^{11}$	$1.8 \times 10^{12}  (640  \mathrm{nm})$	$10^{12}$ 1.7/1.0 $\mu s$ 5.4 $\times$ 10 <sup>12</sup> (532 nm) 597 ns(TPC extracted) <sup>b</sup>	$(6.0 \pm 1.3) \times 10^{12}$	$1.23\times 10^{13}$
Dark current (density) ( $I_{\rm d}$ or $J_{\rm d}$ )	$2.2 \times 10^{-9} \mathrm{A  cm^{-2}} (-0.1 \mathrm{V},$	about 3 dines reduced)	$7.84 \times 10^{-6} \text{ mA cm}^{-2} (0 \text{ V}, \text{about 4 times reduced})$	$2.3 \times 10^{-27} \mathrm{A}^2 \mathrm{Hz}^{-1}$ (noise signal) <sup>a</sup>	51811d1) —	$6.0 \times 10^{-6} \text{ mA cm}^{-2} (-0.3 \text{ V},$	about 600 times reduced) $<10^{-13}  \mathrm{A  Hz^{-1/2}}$ (noise	signal) $1.8 \times 10^{-8} \text{ mA cm}^{-2} (-0.05 \text{ V}, 1.2 \times 10^{12} (450 \text{ nm}) 3/6 \mu s$	about 10 unies reduced) $10^{-10}  {\rm A}  (0  {\rm V},  {\rm about}  100  {\rm times}   10^{12}$	$0.042 \times 10^{-6} \text{ A cm}^{-2} (-0.1 \text{ V}, 10^{13} \text{ cm}^{-2})$	about 38 times reduced) $0.030\pm0.004~\mathrm{nA~cm^{-2}}$	$3.25\times 10^{-11}~{\rm A~cm}^{-2}~(-0.5~{\rm V})$	$2.3 \times 10^{-6} \text{ mA cm}^{-2} (-0.01 \text{ V}, 1.1 \times 10^{13}) (532 \text{ nm}) 3.0/2.2 \mu s$	10 <sup>-11</sup> A (about 1000 times	$2.2 \times 10^{-8} \mathrm{A  cm^{-2}} (-0.1 \mathrm{V},$	about 10 times reduced) $10^{-11}$ A (about $10^4$ times	reduced) $9.1 \times 10^{-9}  \mathrm{A  cm^{-2}}  (-2  \mathrm{V}, -2)  \mathrm{Cm^{-2}}  (-2  \mathrm{V}, -2)  $		I	1	ı	$5 \times 10^{-10} \text{ A cm}^{-2} \left(-0.5 \text{ V}\right)$ 1.5 × $10^{-14} \text{ A Hz}^{-1/2} \left(\text{noise signal}\right)^a$	$0.012 \pm 0.005~\mu\mathrm{A~cm}^{-2}$	
Device structure	oped ITO/Mg-doped NiO/MHP/ $C_{60}/BCP/Cu$	ITO/CuInSe <sub>2</sub> quantum dots: PEDOT:PSS/ O- MHP/PCBM/Ag	$\lambda_x$ as ITO/NiO <sub>x</sub> /MHP/PCBM/ZnO/BCP/Al	O- ITO/PEDOT:PSS/PTAA/MHP/PCBM/Phen-NaDDO/Ag		TAA ITO/PTAA/PEIE/MHP/PCBM/BCP/Ag	o- FTO/TiO <sub>2</sub> /MHP/Spiro-OMeTAD/Au	PVP ITO/SnO <sub>2</sub> /PVP/MHP/Spiro-OMeTAD/Au	opti- FTO/Bi-TiO <sub>2</sub> /MHP/Ag	3HT- ITO/P3HT-COOH/MHP/PCBM/PEI/Ag	L, ITO/PEDOT:PSS or NiO <sub>x</sub> /MHP/PCBM or PTCDI/TiO <sub>2</sub> /Al	en ITO/PTAA/PVP/MHP/PCBM/C <sub>60</sub> /TiN/Ag	ITO/PEDOT:PSS/MHP/PCBM:PMMA/Al	nd FTO/Al <sub>2</sub> O <sub>3</sub> /MHP/TiO <sub>2</sub> /Au	ITO/rGO:TS-CuPc/MHP/PCBM/BCP/Ag	luce ITO/NiO <sub>x</sub> /MHP/TiO <sub>2</sub> /Au	FPD ITO/OTPD/MHP/PCBM/C <sub>60</sub> /BCP/Al	ITO/PEDOT:PSS or NiO <sub>x</sub> /MHP/C <sub>60</sub> /BCP/Au	$\mathrm{LiO}_2/\ \mathrm{ITO/TiO}_2/\mathrm{PC}_{61}\mathrm{BM/MHP/P3HT/MoO}_3/\mathrm{Ag}$	uce FTO/TiO <sub>2</sub> /MHP/Au	tT as ITO/ZnO/MHP/P3HT/MoO₃/Ag	ITO/PEDOT:PSS/MHP/PCBM/C <sub>60</sub> /LiF/Au crys- ITO/PTAA/Al <sub>2</sub> O <sub>3</sub> /MHP/PMMA/PCBM/BCP <sub>1</sub> rface Ag	FTO/TiO <sub>2</sub> , Al <sub>2</sub> O <sub>3</sub> , PCBM/MHP/Spiro-	OMCLAD/AS,AU ITO/Li doped VO <sub>x</sub> /MHP/PCBM/BCP/Ag
Strategy	Reduce interface defects and optimize crystallinity (Mg doped ITO/Mg-doped NiO/MHP/C <sub>60</sub> /BCP/Cu NiO as an ERI)	Regulate band alignment, reduce interface defects and increase optical absorption (CuInSe <sub>2</sub> quantum dots: PED-OT-PSE as a hybrid FRI)	Regulate band alignment and optimize crystallinity (NiO <sub>x</sub> as ITO/NiO <sub>x</sub> /MHP/PCBM/ZnO/BCP/Al an FRI.)	Regulate band alignment and optimize crystallinity (PED-OT-POPTAA as a double-FRI)	Optimize crystallinity (Nafion modified PEDOT:PSS EBL)	Optimize morphology and crystallinity (PEIE modified PTAA ITO/PTAA/PEIE/MHP/PCBM/BCP/Ag	substrate)  Regulate band alignment (introduction of TiO <sub>2</sub> and Spiro-	OMETAD as interfacial tayers) regulate band alignment and reduce interface defects (PVP	moduned since as an riber) Regulate band alignment, reduce interface defects and opti- FTO/Bi-TiO <sub>2</sub> /MHP/Ag mize mombholoov (AID TiO, Sehin-coated TiO, as HRI s)	ming in the principal of the property of the p	COOH as an EBL) Regulate band alignment (PEDOT:PSS or NiO <sub>x</sub> as an EBL, PCBM or PTCDI as an HBL)	Regulate band alignment (TiN as a blocking layer between MHP and electrode)	Regulate band alignment (PCBM:PMMA as an HBL)	Optimize morphology and crystallinity, and regulate band	Regulate band alignment and reduce interface defects	(FGO:1S-CuPc nanocomposites as the interfacial layer) Regulate band alignment, optimize morphology and reduce ITO/NiO <sub>x</sub> /MHP/TiO <sub>2</sub> /Au :	interface defects (ND <sub>x</sub> and 110 <sub>2</sub> as interfactal tayers)  Regulate band alignment and reduce surface defects (OTPD ITO/OTPD/MHP/PCBM/C <sub>60</sub> /BCP/Al	as an LDL and FORM/C <sub>60</sub> as TIDLS) Regulate band alignment (NiO <sub>x</sub> as an EBL)	Regulate band alignment and reduce interface defects (TiO <sub>2</sub> / ITO/TiO <sub>2</sub> /PC <sub>61</sub> BM/MHP/P3HT/MoO <sub>3</sub> /Ag	receive as traces. Optimize morphology, regulate band alignment and reduce ${ m FTO/TiO_2/MHP/Au}$ interface defeate (TiO as an HBI)	niteriace defects (1102 as an ribb.) Reduce surface defects and regulate band alignment (P3HT as ITO/ZnO/MHP/P3HT/MoO <sub>3</sub> /Ag an FRI)	Regulate band alignment (PCBM/C <sub>60</sub> as HBLs) ITO/PEDOT:PSS/MHP/PCBM/C <sub>60</sub> /LiF/Au Reduce interface defects and optimize morphology and crys- ITO/PTAA/Al <sub>2</sub> O <sub>3</sub> /MHP/PMMA/PCBM/BCP/ tallinity (Al <sub>2</sub> O <sub>3</sub> as a bottom interlayer and PMMA as a surface Ag	Regulate band alignment (TiO <sub>2</sub> , Al <sub>2</sub> O <sub>3</sub> , PCBM as HBLs)	Reduce interface defects (Li doped $\mathrm{VO}_x$ as an EBL)

Review

lable 4 (continued)					
Strategy	Device structure	Dark current (density) ( $I_d$ or $D^*$ (Jones)	Speed [rise time $(t_t)$ / LDR fall (decay) time $(t_t)$ ] (dB)		Ref.
		$3.38 \times 10^{-9} \text{ A cm}^{-2} (-0.1 \text{ V}, 0.00)$	0.29  µs (TPC)		
Reduce surface defects (PCBM and aluminum doped ZnO as ITO/PEDOT:PSS/MHP/PCBM/AZO/Al	nO as ITO/PEDOT:PSS/MHP/PCBM/AZO/Al	$1.4 \times 10^{-7}  \mathrm{A  cm^{-2}}  (-1  \mathrm{V})$	100 ns (TPC	57	145
HBLs) Optimize morphology (PC $_{60}$ BM or PC $_{70}$ BM as HBLs)	ITO/PEDOT:PSS/MHP/PC <sub>60</sub> BM or	$33.41  ext{ fA Hz}^{-1/2}  ext{ (noise signal)}^a 2.05  imes 10^{12}$	extracted) $^{o}$ 150.2/159.7 ns	>90 146	146
PC $_{70}$ BM/BCP/Ag Reduce surface defects (Cs $_{0.1}$ MA $_{0.3}$ FA $_{0.6}$ )AgBil, as an interface ITO/NiO $_{3}$ /MHP/SnO $_{2}$ /Au	PC <sub>70</sub> BM/BCP/Ag erface ITO/NiO <sub>x</sub> /MHP/SnO <sub>2</sub> /Au	$17.5 \text{ pA cm}^{-2}$ 0.43 $\mu \text{Gy s}^{-1}$	0.2/0.5 s	I	147
layer for Cs <sub>0.05</sub> MA <sub>0.65</sub> FA <sub>0.3</sub> PbI <sub>3</sub> )		$(detection limit)^c$	$mit)^c$		

<sup>a</sup> Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various frequencies. <sup>b</sup> TPC extracted: speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurrent curves. frequencies. <sup>b</sup> TPC extracted speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurre contract greater than three times the noise current (dark current).

Fig. 11c. 149 The inclusion of rigid SrTiO<sub>3</sub> not only increased device stability by preventing anion interdiffusion between CsPbBr<sub>3</sub> and SrTiO<sub>3</sub>, leading to an effective operating temperature of 150 °C for the MHPPD, but also facilitated the formation of a sharp P-N interface with CsPbBr3, ensuring low Jd and satisfactory photoresponse. Furthermore, Wang et al. demonstrated a P-I-N heterojunction (n-type, Bi-doped MAPbBr<sub>3</sub>)/ (intrinsic, MAPbBr<sub>2.5</sub>Cl<sub>0.5</sub>)/(p-type, Ag-doped MAPbBr<sub>3</sub>) by a solution-processed dopant incorporated epitaxial growth method. 150 To identify suitable dopants, researchers investigated the thermal-probe-induced effects of MHPs incorporating different dopants. After optimization, 0.1 M AgBr-doped and 0.2 M Bi-doped MAPbBr<sub>3</sub> were grown on opposite faces of the MAPbBr<sub>2.5</sub>Cl<sub>0.5</sub> substrate to form a P-I-N heterojunction (Fig. 11d). Benefiting from the efficient P-I-N junction, which provides sufficient charge barriers and facilitates energy alignment, the MHPPDs exhibited a low  $J_d$  of 11 nA cm<sup>-2</sup> under 500 V cm<sup>-1</sup> and a lowest detection limit of 16 nGy s<sup>-1</sup>. More recently, Zou and colleagues developed a dual-band heterojunction configuration of MAPbBr<sub>3</sub>/PCBM/FASn<sub>0.5</sub>Pb<sub>0.5</sub>I<sub>3</sub> using a high-throughput blading method for ultra-fast MHz imaging and communication speeds (Fig. 11e). 151 This dual-band heterojunction, benefiting from the absorption of both wide (MAPbBr<sub>3</sub>) and narrow (FASn<sub>0.5</sub>Pb<sub>0.5</sub>I<sub>3</sub>) MHPs and tuning of the polarity and amplitude of the bias voltage, enabled MHPPDs based on this structure to achieve a  $D^*$  of 1.25/3.10  $\times$  10<sup>12</sup> Jones and bandwidths of 16.5/>20 MHz for the visible/ NIR bands.

Additionally, researchers have developed MHP heterojunctions incorporating narrow band gap ionic dyes (Fig. 12a) and QDs (Fig. 12b) to extend light absorption deep into NIR regimes and effectively suppress device J<sub>d</sub> through precise gradient energy alignment design. 152,153 For the UV regime of the heterojunction in MHPPDs, Ga<sub>2</sub>O<sub>3</sub> (Fig. 12c) and ZnO (Fig. 12d) were employed to achieve efficient carrier separation and broaden the photoresponse of MHPPDs. 154,155 Table 5 compares the performance parameters of recent MHPPDs based on various heterojunctions.

#### 5.6 Architecture modification

The device architecture plays a crucial role in reducing  $I_d$  and enhancing the FOMs of MHPPDs. By controlling the stacking type of materials, manipulating the electrodes, and incorporating extra devices into the MHPPDs, it is possible to efficiently mitigate  $J_d$  and increase the FOMs of MHPPDs. For example, Song et al. designed lateral P-I-N single crystal MHPPDs to isolate the electrodes from contacting the MHP surface, in contrast to conventional metal-semiconductor-metal photodiodes, as illustrated in Fig. 13a.180 The resulting devices exhibited nearly three orders of magnitude suppression of  $I_d$ compared to the metal-semiconductor-metal devices. Moreover, they demonstrated environmental stability by avoiding the interfacial electrochemical reaction between the electrode and MHP. In another approach, Jin et al. developed a MHPPD architecture by adding a shunting electrode as a blanking unit to suppress  $J_d$ . <sup>181</sup> As depicted in Fig. 13b, electrons are emitted

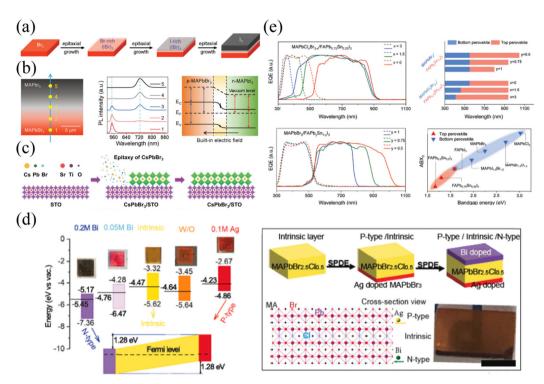


Fig. 11 (a) Epitaxial growth process of the MHP heterojunction. (b) Positions for PL measurements (left), PL spectra (middle), and band diagram of the MHP heterojunction without bias (right). Reproduced with permission. 148 Copyright 2023, Wiley-VCH. (c) Schematic diagram of the vapor-phase epitaxy of the CsPbBr<sub>3</sub> thin film on halide-oxide perovskite. Reproduced with permission. 149 Copyright 2023, Wiley-VCH. (d) Energy diagram and the fabrication process of the MHP heterojunction by doping in the epitaxial growth. Reproduced with permission. Copyright 2021, Elsevier. (e) Optoelectronic properties of the double MHP heterojunction thin films. Reproduced with permission. 151 Copyright 2024, Wiley-VCH.

from the source to the drain electrode with two lateral terminals in the dark. To minimize the absolute value of  $J_d$ , a top dark-current-shunting electrode on the MHP films was utilized to attract the emitted electrons, leading to effective shunting of mobile electrons under dark conditions. This design resulted in an ultra-low  $J_d$  of 51.1 pA cm<sup>-2</sup> and a detection limit of 7.84 nGy  $s^{-1}$ . Additionally, Zhan et al. introduced a modification to the device structure by presenting a MHPPDs crossbar array through vapor deposition. 182 This array consisted of a P-I-N diode (ITO/PEDOT:PSS/MHP/PCBM/BCP) and a reverse blocking diode (PCBM/BCP/PbI<sub>2</sub>/Spiro-TTB) in a vertically stacking sequence, with PCBM/BCP serving as the co-cathode, as shown in Fig. 13c. The presence of the blocking diode established an efficient barrier to prevent electron transfer to the Ag electrode. This configuration is fully scalable and compatible with integrated circuits, making it suitable for the industrialization of image sensors. The devices and the corresponding strategies for architecture modification and performance parameters are summarized in Table 6.

## 6. Summary and perspectives

Due to their remarkable optical and electrical properties, MHPPDs have showcased unparalleled performance, surpassing commercially available inorganic counterparts in recent years. In addition, formidable progress has been made in developing robust optoelectronic applications such as static

imaging for visible and X-ray spectra, 141,186 real-time dynamic imaging, 182 communications, 102,107 and health monitoring. 91,187 Despite this, MHPPDs still face challenges related to defects within their structure that impair the dynamics of charge carriers, diminishing photodetection performance metrics like  $J_d$ , LDR,  $D^*$ , and speed. To address these issues, a deep understanding of  $J_d$ 's origin in MHPPDs is critical. Research has been directed towards component and dimensional engineering to mitigate defects within the bulk and interfaces, interfacial engineering, the integration of heterojunctions, and adjustments to device architectures. Tables 1-6 encapsulate the enhancements in  $J_d$  and other FOMs demonstrated using these strategies. Future research targeting superior performance and durability in optoelectronic devices, facilitating detection across a broad spectral range from ionizing radiation to near-infrared, is indispensable. Achieving high EQE or R while simultaneously suppressing the  $J_d$  in MHPPDs is critical and challenging. Both EQE (or R) and  $J_d$  are highly dependent on carrier generation, extraction, and recombination processes. The efficiency of these processes directly impacts EQE (or R) and  $J_d$ . For instance, the quality of the MHP films and the interfaces between the MHP and the EBL as well as the HBL are essential for influencing charge transportation and recombination, thereby impacting EQE (or R) and  $J_d$ . The mobility and stability of the EBL and HBL are highly relevant to charge extraction and recombination at the interface between MHP and EBL/HBL, thereby also affecting EQE (or R)

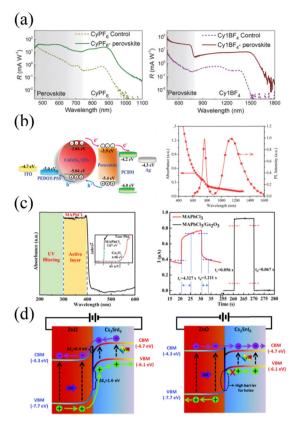


Fig. 12 (a) Photoresponse of the CyPF<sub>6</sub>, Cy<sub>1</sub>BF<sub>4</sub>, and MHP-CyPF<sub>6</sub>, Cy<sub>1</sub>BF<sub>4</sub> heterojunction MHPPDs. Reproduced with permission. 152 Copyright 2017, Wiley-VCH. (b) Energy band diagram of the MHP/CulnSe2 QDs heterojunction (left), the absorption and PL spectra of the MHP/CuInSe<sub>2</sub> QD thin film (right). Reproduced with permission. 156 Copyright 2020, Wiley-VCH. (c) Absorption spectrum and bandgap of MAPbCl<sub>3</sub> and amorphous Ga<sub>2</sub>O<sub>3</sub> films (left), the I-t curves of the MAPbCl<sub>3</sub>/amorphous Ga<sub>2</sub>O<sub>3</sub>-based devices (right). Reproduced with permission. 157 Copyright 2022, Elsevier. (d) Energy band diagram showing the band alignment and carrier dynamics of the CsSnI<sub>6</sub>/ZnO device under different biases. Reproduced with permission. 155 Copyright 2020, RSC.

and  $J_d$ . Furthermore, mechanical stress at the interface between MHP and EBL/HBL can introduce defects that deteriorate EQE (or R) and  $J_d$ . Therefore, by employing advanced passivation techniques, improved fabrication methods, and optimized device architectures aimed at increasing the quality of the MHP film, EBL/HBL, and the interface between MHP and EBL/HBL, it is possible to develop MHPPDs with high EQE (or R) and low  $J_d$ .

Central to advancing MHPPDs is an in-depth understanding of the origins of  $J_d$ . Current research predominantly employs the conventional semiconductor-based photodiode model grounded in thermodynamics. However, given MHPs' ionic characteristics, it is pivotal to develop a nuanced MHPPD model accounting for ion migration within the bulk and interfaces—an imperative for light sensing and direct radiation detection applications. A comprehensive model must also incorporate interactions between MHPs, CTLs, and electrodes to thoroughly describe charge carrier behavior under dark conditions.

Addressing the defects present in MHPs is the crucial strategy for substantially reducing the  $J_d$  in MHPPDs. These defects, located in the bulk and at the interfaces of MHPs, are recognized as major contributors to elevated J<sub>d</sub> levels and undesirable periods of  $J_d$  drift in MHPPDs. Thankfully, numerous effective strategies have emerged which include component, additive, and interfacial engineering. Among these, strategic component selection is particularly promising in mitigating issues such as ion migration and phase transitions caused by these defects. Monovalent cations like FA are highly competitive in MHPs used in MHPPDs for broadband light detection, owing to their lower bandgap and improved thermal and light stability compared to other cations. Similarly, the choice of halide ions plays a critical role. Beyond just tuning the absorption spectrum of the devices, previous studies have highlighted the beneficial effects of various halide anions on the crystallization process and defect suppression in MHP films. Notably, Cl<sup>-</sup> and bromine Br<sup>-</sup> ions, at certain concentrations, can enhance crystallinity, morphology, and stability of MHPs, which in turn boosts photodetection performance.

Passivation techniques involving additives in MHP precursor solutions and interfacial engineering are critical for defect suppression and overall device performance enhancement. It is imperative to develop thoughtful additive design strategies and more resilient CTLs that consider the multifunctional effects of additives and the complexities of surface defect configurations. Moreover, there is a need for continued research into strategies for constructing heterojunctions either with MHPs or with other superior optoelectronic materials. These heterojunctions could help in managing surface defects, aligning energy bands, and improving optoelectronic properties, thus potentially mitigating  $J_d$  and minimizing periods of  $J_d$  drift in MHPPDs.

Further rethinking of the architecture of MHPPDs can serve to effectively suppress  $J_d$ . Introducing additional layers, such as EBL or HBL, can prevent charge carriers from being injected from the electrodes into the MHP, thereby reducing  $J_d$ . The alignment of material energy levels, as well as both vertical and lateral architectural designs, are crucial in influencing the charge dynamics within the device. Additionally, the implementation of electrical regulation methods can effectively curb  $J_{\rm d}$  and further diminish  $J_{\rm d}$  drift periods. <sup>181,188</sup> Future research should focus on simplifying device structures and developing strategies suitable for large-scale industrial production.

Controlling the operational temperature of MHPPDs has shown potential in minimizing J<sub>d</sub> and enhancing device performance. Lower temperatures effectively restrain thermal excitation of charge carriers, thereby reducing  $J_{\text{diff}}$  generation. This temperature-dependent suppression offers promising prospects for achieving enhanced D\* in MHPPDs. Moreover, operating at cooler temperatures can increase the stability and lifespan of MHP films by curbing degradation processes. However, maintaining an optimal temperature is essential; excessively low temperatures may impair the device's response time and sensitivity. Therefore, it is critical to finely tune the

**Table 5** Summary of the heterojunctions with MHP for suppressing  $J_d$  and enhancing the FOMs of MHPPDs

Strategy	Device structure	Dark current (density) $(I_{ m d} \ { m or} \ J_{ m d})$	$D^*$ (Jones)	Speed [rise time $(t_r)$ /fall (decay) time $(t_f)$ ]	LDR (dB)	Ref.
Generate injection barrier and reduce interface defects (MAPbBr <sub>3</sub> /Bi <sup>3+</sup> -doped MAPbCl <sub>3</sub> single	Au/MAPbBr <sub>3</sub> /Bi <sup>3+</sup> -doped MAPbCl <sub>3</sub> /Au	0.78 nA (-100 V)	ı	4.89 $\mu s$ (TPC extracted) <sup>b</sup>	1	159
crystals) Establish the built-in electrical field	FTO/NiO <sub>x</sub> /MHP/Ag	$1.3 \times 10^{-12} \mathrm{A~Hz}^{-1/2} \; \mathrm{(noise~signal)}^a$	$1.3\times 10^{11}$	3.04/4.66 ms	116.6	160
Establish the built-in electrical field (CsPbBr <sub>3</sub> /	ITO/SnO <sub>2</sub> /CsPbBr <sub>3</sub> /Cs <sub>4</sub> PbBr <sub>6</sub> /	63 nA cm <sup>-2</sup> (4 V, about 1.3 times	$^{15} \text{ nGys}^{-1}$ (detection	1.6/1.2 ms	I	156
CS <sub>4</sub> PDBf <sub>6</sub> )  Regulate band alignment (GaN/CS <sub>2</sub> AgBiBf <sub>6</sub> /NiO) In/GaN/MHP/NiO/Au  Establish the built-in electrical field (MAPbCl <sub>3</sub> /Bi³ <sup>-</sup> - Ag/MAPbCl <sub>3</sub> /Bi³ <sup>-</sup> -doped MAPbCl <sub>3</sub> Annel MABFCl cincils constale.	P3HT:PCBM/Au In/GaN/MHP/NiO/Au Ag/MAPbCl <sub>3</sub> /Bi <sup>3+</sup> -doped MAPbCl <sub>3</sub>	reduced) $1.89 \times 10^{-9}  \mathrm{A}  (0  \mathrm{V})$ $2.15  \mathrm{\mu A}  \mathrm{cm}^{-2}  (-20  \mathrm{V})$	mint) 3.28 $\times$ 10 <sup>11</sup> (365 nm) 4.87 $\times$ 10 <sup>11</sup> (393 nm)	151/215 µs 176.3 ns/11.6 µs	1 1	157 158
surged war DC3 single crystans)  Establish the built-in electrical field (PVP-modified Au/MHP/Si/Au	Strigic Crystals/Au Au/MHP/Si/Au	I	$1.5 \times 10^{12} \ (405 \ \mathrm{nm})$	645/560 µs	44	161
MAPbCl <sub>3-x</sub> I <sub>x</sub> /Si) Establish the built-in electrical field (planar-type	Pt/Ag*-doped MAPbBr <sub>3</sub> /Sb <sup>3+</sup> -	$300 \text{ fA Hz}^{-1/2} (0 \text{ V})$	$6.39 \times 10^{11} (530 \text{ nm})$	14/10 ms	1	162
Ag -uopeu Mar Dhis/So -uopeu Mar Dhis) Establish the built-in electrical field (Marbbr C) /Marbbc)	uopeu MAFDB13/Ag Au/Poly-TPD/MAPbBr <sub>2.5</sub> Cl <sub>0.5</sub> / MAPhCl /Ag	$1.12 \times 10^{-10} \text{ A Hz}^{-1/2} \text{ (noise signal)}^a$	$7.32\times10^7~(500~\mathrm{nm})$	10/15 µs		163
Establish the built-in electrical field (ZnO/Cs <sub>2</sub> SnI <sub>6</sub> ) ITO/ZnO/MHP/Al	ITO/ZnO/MHP/Al	(-100  V) 0.15 pA Hz <sup>-1/2</sup>	$1.39 \times 10^{12} (378 \text{ nm})$	4.3/5.2 µs	119	155
Establish the built-in electrical field (Si/SnO <sub>2</sub> /	Al/Si/SnO <sub>2</sub> /MAPbI <sub>3</sub> /MoO <sub>3</sub> /Ag	0.13 nA	$2.23 \times 10^{12}  (815  \mathrm{nm})$	13.0/14.6 ms		164
MAPDI3/MOO3) MAPDI3/MOO3) MAPDI3/MOO3) MAPDI3/MOO3) MAPDI3/MOO3	${\rm ITO/ZnO/MHP/PTAA/MoO_{x}/Ag}$	$5.46  ext{ fA Hz}^{-1/2}$ (about $20\%$ reduced)	$6.07 \times 10^{11}  (390 \; \mathrm{nm})$	28/— µs		165
MAPDCI3) Reduce interface defects and regulate band align- ITO/PTAA/MHP/O6T-4F/C <sub>60</sub> /BCP/	ITO/PTAA/MHP/06T-4F/C <sub>60</sub> /BCP/	$3.57 \times 10^{-10}$ MA cm <sup>-2</sup> (-0.5 V, about 1.06 × 10 <sup>15</sup> (500 nm)	$1.06 \times 10^{15}  (500 \; \mathrm{nm})$	2.9/4.8 µs	110	166
ment (2D/3D MHP/O61-4F) Establish the built-in electrical field (MAPbl <sub>3</sub> /TiO <sub>2</sub> ) FTO/TiO <sub>2</sub> /MHP/Spiro-OMeTAD/	AI   FTO/TiO <sub>2</sub> /MHP/Spiro-OMeTAD/	8 times reduced) -5 nA (0 V)	$7.8 \times 10^{10}  (494  \mathrm{nm})$	I		167
Establish the built-in electrical field	Au ITO/MHPs/Cr/Au	$10^{-6}\mathrm{Acm}^{-2}(\mathrm{about}10^3\mathrm{times}\mathrm{reduced})$	I	150/170 ms	I	168
((BA)2(WA)F0247(BA)2F034(BA)2(WA)F0247) Establish the built-in electrical field and increase	FTO/MHP/NiO/Au	I	$10^{10}$	$320 \pm 10/305 \pm 10 \text{ ms}$	I	169
optical absorption (NIO/)MAPD13/ Regulate band alignment and increase optical	FTO/PEDOT:PSS/CuInSe <sub>2</sub> quan-	8.7 fA $\mathrm{Hz}^{-1/2}$ (noise signal) <sup>a</sup>	$7.0 \times 10^{10}  (580  \mathrm{nm})$	277 ns (TPC extracted) <sup><math>b</math></sup>	75.16	153
Establish the built-in electrical field and impede	Au/CsPbBr <sub>3</sub> /SrTiO <sub>3</sub> /Ag	$2.01  imes 10^{-12}  ext{ A (-1 V)}$	$7.7 \times 10^{11} (850 \text{ nm})$ $2.98 \times 10^{13}$	2.06/0.30 s	1	149
the anion interdiffusion (CsPbBr <sub>3</sub> /SrHO <sub>3</sub> ) Establish the built-in electrical field (SnO <sub>2</sub> /	FTO/SnO <sub>2</sub> /MHP/Au	2 nA (about 280 times reduced)	$2.1\times 10^{12}$	248/341 µs	108	170
Cospagning) Reduce interface defects and increase optical	ITO/PTAA/MHP/	$8.7 \times 10^{-5} \text{ mA cm}^{-2} (-0.3 \text{ V, about})$	$1 \times 10^{11} \ (900 \ \mathrm{nm})$	5 ns (TPC extracted) $^b$	95	171
absorption (whe big territoring)  Establish the built-in electrical field (MAPbI <sub>3</sub> /PTB7/ ITDPDT:PSS/MHP/PTB7/C <sub>60</sub> /	' ITO/PEDOT:PSS/MHP/PTB7/C <sub>60</sub> /	$1.85 \times 10^{-5} \mathrm{mA  cm^{-2}} (-0.1 \mathrm{V})$	$1.37 \times 10^{12} (680 \text{ nm})$	3.9/4 µs	141	172
Coo) Establish the built-in electrical field (MAPbBr <sub>3-n</sub> Cl <sub>n</sub> /CsPbBr <sub>3</sub> )	BCF/Ag Au/MAPbBr <sub>3-n</sub> Cl <sub>n</sub> /CsPbBr <sub>3</sub> /Au	0.5 $\mu$ A cm <sup>-2</sup> 3.92 × 10 <sup>-4</sup> nA cm <sup>-1</sup> s <sup>-1</sup> V <sup>-1</sup> (drifting) <sup>d</sup> (-125 V mm <sup>-1</sup> , about 100 times	96 nGy s $^{-1}$ (detection limit) $^{c}$	I	I	173
Establish the built-in electrical field (MAPbCl <sub>3</sub> /	Au/MAPbCl <sub>3</sub> /MAPbBr <sub>3</sub> /Au	seduced) 300 nA (about 5 times reduced)	$7  imes 10^{11}$	0.43/1.39 s	I	174
wAr DDI 3 single crystal) Establish the built-in electrical field (Bi-doped MAPbBr <sub>3</sub> /MAPbBr <sub>2,5</sub> Cl <sub>0,5</sub> /Ag-doped MAPbBr <sub>3</sub> )	Au/Bi-doped MAPbBr <sub>3</sub> / MAPbBr <sub>2,5</sub> Cl <sub>0,5</sub> /Ag-doped MAPbBr <sub>3</sub> /Au	11 nA cm $^{-2}$ ( $-0.07$ V)	16 nGy s $^{-1}$ (detection limit) $^{\ell}$	—/750 ns	1	150

Published on 08 2024. Downloaded on 16/10/2025 08:32:40.

Review

(continued) Table 5

Strategy	Device structure	Dark current (density) ( $I_{ m d}$ or $J_{ m d}$ )	$D^*$ (Jones)	Speed [rise time $(t_i)$ /fall (decay) time $(t_i)$ ]	LDR (dB)	Ref.
Establish the built-in electrical field and regulate Au/MAPbCl <sub>3</sub> /MAPbBr <sub>3</sub> /Au	Au/MAPbCl <sub>3</sub> /MAPbBr <sub>3</sub> /Au	1	12.2 nGy s <sup>-1</sup> (detection 1.5/1.6 ms $\lim_{i \to i+jc}$	1.5/1.6 ms	I	148
band anginnent (war bots) ware but single ciystal bands a Au/Cs <sub>2</sub> AgBiBr <sub>6</sub> / $(C_{38}H_{34}P_2)MnBr_4/$ 20 pA Hz <sup>-1/2</sup> (noise signal) <sup>a</sup> for the bult-in electrical field $(C_{52}AgBiBr_6/(C_{38}H_{34}P_2)MnBr_4/$ 20 pA Hz <sup>-1/2</sup> (noise signal) <sup>a</sup> for the bult-in electrical field $(C_{52}AgBiBr_6/(C_{38}H_{34}P_2)MnBr_4/$ 20 pA Hz <sup>-1/2</sup> (noise signal) <sup>a</sup>	$Au/Cs_2AgBiBr_6/(C_{38}H_{34}P_2)MnBr_4/C_{18CD/Cr}$	20 pA $\mathrm{Hz}^{-1/2}$ (noise signal) <sup>a</sup>	mme) 0.2 μGy (detection limit)	$^{0.01}_{0.2}$ $^{0.02}_{0.2}$ $^{0.02}_{0.2}$ $^{0.02}_{0.2}$ $^{0.02}_{0.2}$ $^{0.02}_{0.2}$	I	175
(C38H34F2)MIID(4)	C60/BOE/O	$5.3 \times 10^{-7} \mathrm{nA} \mathrm{cm}^{-1} \mathrm{s}^{-1} \mathrm{V}^{-1} (\mathrm{drifting})^d$				
Regulate band alignment and establish the built-in Carbon/ $Cs_{0.15}FA_{0.85}P$ -electrical field $(Cs_{0.15}FA_{0.85}Pb(I_{0.15}Br_{0.85})_3/Cs_{0.15}FA$	Carbon/Cs <sub>0.15</sub> FA <sub>0.85</sub> P- 0.701 nA cm <sup>-2</sup> (0.701 nA cm <sup>-2</sup> b(I <sub>0.15</sub> Br <sub>0.85</sub> ) <sup>3</sup> /Cs <sub>0.15</sub> FA <sub>0.85</sub> PbI <sub>3</sub> /Cs <sub>60</sub> / times reduced)	0.701 nA cm <sup>-2</sup> / $(-25 \text{ V, about } 200 \text{ times reduced})$	$13.8\pm0.29~{ m nGy~s^{-1}}$ (detection limit) $^c$	6.1 µs	I	176
CS <sub>0.15</sub> FA <sub>0.85</sub> PbI <sub>3</sub> ) Establish the built-in electrical field (MAPbI <sub>3</sub> )	BCP/Cr ITO/PEDOT:PSS/MHP/	1 <sup>-2</sup> (-0.1 V, about 5	$3 imes 10^{13}$	4.82/4.30 µs	112	177
FDFF31:PC <sub>71</sub> BMJ Establish the built-in electrical field and increase optical absorption (MAPbJ <sub>3</sub> :graphene quantum	PDPP31:PC <sub>71</sub> BM/A1 InGa/BCP/Si/P-Si/MHP/Au	times reduced) —	$7.6\times10^{10}$	654/735 ns	80	178
dots/Porous Si) Establish the built-in electrical field and increase	FTO/Ga <sub>2</sub> O <sub>3</sub> /MHP/Spiro-OMeTAD/	FTO/Ga <sub>2</sub> O <sub>3</sub> /MHP/Spiro-OMeTAD/ 1.042 nA (about 330 times reduced) $5.4 \times 10^{10}$	$5.4\times10^{10}$	56/67 ms	80	154
optical absorption (MAPbCl <sub>3</sub> /amorphous Ga <sub>2</sub> O <sub>3</sub> ) Establish the built-in electrical field and increase	Ag FTO/PEDOT:PSS/MHP/PCBM/	1.3 $\times$ 10 <sup>-10</sup> mA cm <sup>-2</sup> (-0.5 V, 7000 1.25 $\times$ 10 <sup>12</sup>	$1.25\times10^{12}$	124.5/37.2 ns	102	151
optical absorption (MAPBE <sub>3</sub> /FANn <sub>0.5</sub> Nn <sub>0.5</sub> Nn <sub>0.5</sub> l <sub>3</sub> ) Establish the built-in electrical field and increase	MHP/P3HT/Ag ITO/SnOx/MHP/PM <sub>6</sub> :BTP-	times reduced) 3.74 nA cm $^{-2}$ $(-0.2 \text{ V})$	$>10^{13} (800-900 \text{ nm})$	9.02/11.42 µs		179
opucai absorption (Mrtz/ternary Brtj (FAF013/ PM <sub>6</sub> :BTP-eC9:BTP-2F2Cl-P2TH))	eC9:B1F-ZFZ Cl-P2TH/C <sub>60</sub> /BCP/Ag		$>10^{12} (400-800 \text{ nm})$			

<sup>a</sup> Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various frequencies. <sup>b</sup> TPC extracted: speed here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted from the transient photocurrent curves. <sup>c</sup> Detection limit: the detection limit in X-ray detection is defined as the equivalent dose rate to produce a photocurrent greater than three times the noise current (dark current). <sup>d</sup> Drifting: drifting means the dark current drift period D.

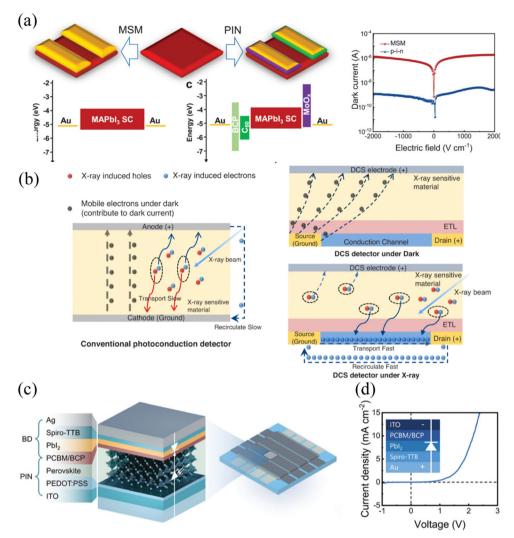


Fig. 13 (a) The schematic diagram, the energy level diagram, and dark current curves of the metal-semiconductor-metal (MSM) and lateral P-I-N devices. Reproduced with permission. 180 Copyright 2021, Wiley-VCH. (b) The schematic illustration of the conventional and dark-current-shunting MHPPD under dark and X-ray radiation. Reproduced with permission. 181 Copyright 2023, Nature. (c) The structure of an integrated PIN-blocking diode. (d) Current-voltage (I-V) curves of the blocking diode. Reproduced with permission: 182 Copyright 2022, Wiley-VCH.

temperature range to strike a balance between suppressing  $J_{\rm d}$ while sustaining overall device effectiveness.

Additionally, thorough testing and accurate characterization of MHPPDs are imperative. 189 Common issues include the overestimation of D\* due to the oversight of noise currents other than  $J_{\rm d},^{190}$  the challenges in testing MHPPDs for direct Xray detection under atmospheric conditions, 191 and incorrect application of formulas or linear fitting in assessing the LDR of MHPPDs. 192 Implementing advanced characterization techniques is fundamental to elucidate the chemical, morphological, structural, and optoelectronic attributes of MHPs, which assist in mitigating  $I_d$  in MHPPDs. Techniques such as UV-visible-NIR spectroscopy, photoluminescence (PL), time-resolved PL, and transient absorption spectroscopy are instrumental in directly assessing the light absorption and luminescence properties of MHPs. Electron microscopies like scanning electron microscopy (SEM), transmission electron microscopy (TEM), atomic

force microscopy (AFM) combined with conductive AFM (c-AFM), and energy-dispersive X-ray (EDX) spectroscopy provide in-depth analysis of chemical, morphological, and structural properties at the interface of MHPs. Depth-profiling techniques, including X-ray photoelectron spectroscopy (XPS) and time-of-flight secondary ion mass spectrometry (TOF-SIMS), are crucial for profiling the chemical composition through the depth of MHPs. Characterization techniques geared towards electrical properties, such as electrochemical impedance spectroscopy (EIS), space-charge-limited currents, and transient photovoltage/photocurrent studies, are critical for investigating charge transport and extraction dynamics in MHPPDs. By leveraging these advanced techniques and refining the associated methodologies, we can better differentiate the performance attributes of MHPs, address their intrinsic challenges, and drive forward the performance of MHPPDs. In conclusion, as research continues to focus on suppressing  $J_d$ 

Summary of the architecture modification in MHPs for suppressing J<sub>d</sub> and enhancing the FOMs of MHPPDs Table 6

	Dark current (density) $I_d$ or		Speed [rise time $(t_r)$ / LDR	// LDR	
Strategy Device structure	$J_{ m d})$ $D^*$ (Jones)	ones)	fall (decay) time $(t_i)$ ] (dB) Ref.	[dB)	Ref.
Regulate band alignment and promote band bending (MAPbI <sub>3</sub> integrated Au/MHP/BP/MoS <sub>2</sub> with a 2D photogate photodiode)	$3 \times 10^{-11} \mathrm{A}$ 1.3 × 10 <sup>12</sup>	$10^{12}$	150/240 µs	111	111 183
Regulate band alignment and promote band bending (PIN PPDs stacked ITO/PEDOT:PSS/MHP/PCBM/BCP/	- 2.1 × 10 <sup>12</sup>	$10^{12}$	61.2/72.8 ns	112	112 182
by a reverse blocking diode and the PCBM/BCP as the co-cathode) Pbl <sub>2</sub> /Spiro-TTB/Ag Regulate band alignment and promote band bending (asymmetric con- Ag/MAPbl <sub>3</sub> /Au	(710  nm) 3.6 × 10 <sup>-16</sup> A Hz <sup>-1/2</sup> (noise 1.3 × 10 <sup>12</sup>	$_{10^{12}}^{ m nm)}$	13.8/16.1 µs	I	184
tact electrodes Ag/MAPb1 <sub>3</sub> /Au)	signal) <sup>a</sup> (520 nm)	nm)			
Establish the built-in electrical field and manage the optical absorption ITO/TaTm:F <sub>6</sub> -TCNNQ/MHP/TaTm:F <sub>6</sub> -	$1.1 \times 10^{-4} \text{ mA cm}^{-2} (-1 \text{ V}, 1.7 \times 10^{12})$	$10^{12}$	25.3 µs (TPC	63	185
(MHP-based photodiode integrated with MHP-based photoconductor) TCNNQ/TaTm/MHP/C <sub>60</sub> /BCP/Ag	about 8 times reduced) (730 nm)	nm)	$extracted)^b$		
Eliminate the interfacial electrochemical reaction (lateral device BCP/C <sub>60</sub> / Lateral Au/BCP/C <sub>60</sub> /MAPbI <sub>3</sub> /MoO <sub>3</sub> /Au	$265 \text{ pA Hz}^{-1/2} \text{ (noise signal)}^a 0.1 \text{ nGy s}^{-1}$	$\mathrm{Gy}~\mathrm{s}^{-1}$	420/470 µs	1	180
$MAPbi_3/MoO_3)$	(about $10^3$ times reduced) (detection limit) <sup><math>c</math></sup>	ction ار			
Impede shunt dark current by employing a top electrode (P-I-N diode Au (source)/C <sub>60</sub> /MHP/Au (drain) and 51.1 fA (5 V mm <sup>-1</sup> )		$7.84 \text{ nGy s}^{-1}$	I	I	181
integrated a dark-current-shunting electrode) PMMA/Au worked as the top electrode	(detection	ction			

a Noise signal: the noise signal in photodetection is recorded by utilizing a fast Fourier transform signal analyzer combined with a preamplifier to capture the noise current at various in X-ray detection is defined as the equivalent dose rate to produce a photocurrent greater than three times the noise current (dark current) here can be defined as the time at which the photocurrent decays from the peak to the original 1/e extracted Detection limit: the detection limit

and improving the reliability and functionality of MHPPDs, their practical application in the field of optoelectronics is becoming increasingly feasible.

## Author contributions

Yue Wang, D. Li, and Q. Song conducted the literature review and drafted the manuscript. Yue Wang, D. Li, Yang Wang, Y. Chen contributed to manuscript editing and grammar check. Yue Wang, D. Li, Q. Song, Y. Liu, Yang Wang and Y. Chen secured funding, resources, supervision, and contributed to manuscript editing.

## Data availability

No primary research results, software or codes have been included and no new data were generated or analysed as part of this review.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the Natural Science Foundation of China (Grant No. 62205062), the Natural Science Foundation of Fujian Province of China (Grant No. 2022J05047, 2023J01087, 2023J01527, 2023J01530), and the Fujian Normal University "Young Talent" Start-up Grant (Grant No. Y0720308K13).

## References

- 1 Z. Li, T. Yan and X. Fang, Nat. Rev. Mater., 2023, 8, 587-603.
- 2 F. Cao, L. Liu and L. Li, Mater. Today, 2023, 62, 327-349.
- 3 S. Mauthe, Y. Baumgartner, M. Sousa, Q. Ding, M. D. Rossell, A. Schenk, L. Czornomaz and K. E. Moselund, Nat. Commun., 2020, 11, 4565.
- 4 R. Tian, X. Gan, C. Li, X. Chen, S. Hu, L. Gu, D. Van Thourhout, A. Castellanos-Gomez, Z. Sun and J. Zhao, Light: Sci. Appl., 2022, 11, 101.
- 5 F. P. García De Arquer, A. Armin, P. Meredith and E. H. Sargent, Nat. Rev. Mater., 2017, 2, 16100.
- 6 Q. Qiu and Z. Huang, Adv. Mater., 2021, 33, 2008126.
- 7 W. Ouyang, J. Chen, Z. Shi and X. Fang, Appl. Phys. Rev., 2021, 8, 31315.
- 8 G. Long, R. Sabatini, M. I. Saidaminov, G. Lakhwani, A. Rasmita, X. Liu, E. H. Sargent and W. Gao, Nat. Rev. Mater., 2020, 5, 423-439.
- 9 Q. Lin, A. Armin, P. L. Burn and P. Meredith, Nat. Photonics, 2015, 9, 687-694.
- 10 Y. Fang and J. Huang, Adv. Mater., 2015, 27, 2804-2810.
- 11 C. Li, H. Wang, F. Wang, T. Li, M. Xu, H. Wang, Z. Wang, X. Zhan, W. Hu and L. Shen, Light: Sci. Appl., 2020, 9, 31.

- 12 C. Chen, Z. Wang, J. Wu, Z. Deng, T. Zhang, Z. Zhu, Y. Jin, B. Lew, I. Srivastava, Z. Liang, S. Nie and V. Gruev, Sci. Adv., 2023, 9, eadk3860.
- 13 S. Tie, S. Dong, R. Yuan, B. Cai, J. Zhu and X. Zheng, Chem. Commun., 2023, 59, 5016-5029.
- 14 P. Kumar, V. K. Shukla, M. Kim and R. Singh, Sens. Actuators, A, 2024, 369, 115076.
- 15 Z. Xiao, Z. Song and Y. Yan, Adv. Mater., 2019, 31, 1803792.
- 16 G. Kakavelakis, M. Gedda, A. Panagiotopoulos, E. Kymakis, T. D. Anthopoulos and K. Petridis, Adv. Sci., 2020, 7, 2002098.
- 17 Q. A. Akkerman, V. D. Innocenzo, S. Accornero, A. Scarpellini, A. Petrozza, M. Prato and L. Manna, J. Am. Chem. Soc., 2015, 137, 10276-10281.
- 18 X. Li, J. M. Hoffman and M. G. Kanatzidis, Chem. Rev., 2021, 121, 2230-2291.
- 19 C. Zhou, H. Lin, Q. He, L. Xu, M. Worku, M. Chaaban, S. Lee, X. Shi, M. Du and B. Ma, Mater. Sci. Eng., R, 2019, **137**, 38-65.
- 20 A. Dey, J. Ye, A. De, E. Debroye, S. K. Ha, E. Bladt, A. S. Kshirsagar, Z. Wang, J. Yin, Y. Wang, L. N. Quan, F. Yan, M. Gao, X. Li, J. Shamsi, T. Debnath, M. Cao, M. A. Scheel, S. Kumar, J. A. Steele, M. Gerhard, L. Chouhan, K. Xu, X. Wu, Y. Li, Y. Zhang, A. Dutta, C. Han, I. Vincon, A. L. Rogach, A. Nag, A. Samanta, B. A. Korgel, C. Shih, D. R. Gamelin, D. H. Son, H. Zeng, H. Zhong, H. Sun, H. V. Demir, I. G. Scheblykin, I. Mora-Seró, J. K. Stolarczyk, J. Z. Zhang, J. Feldmann, J. Hofkens, J. M. Luther, J. Pérez-Prieto, L. Li, L. Manna, M. I. Bodnarchuk, M. V. Kovalenko, M. B. J. Roeffaers, N. Pradhan, O. F. Mohammed, O. M. Bakr, P. Yang, P. Müller-Buschbaum, P. V. Kamat, Q. Bao, Q. Zhang, R. Krahne, R. E. Galian, S. D. Stranks, S. Bals, V. Biju, W. A. Tisdale, Y. Yan, R. L. Z. Hoye, L. Polavarapu and G. C. U. S. National Renewable Energy Lab. Nrel and O. V. S. Univ., ACS Nano, 2021, 15, 10775-10981.
- 21 J. S. Manser, J. A. Christians and P. V. Kamat, Chem. Rev., 2016, 116, 12956-13008.
- 22 C. Neusel, H. Jelitto and G. A. Schneider, J. Appl. Phys., 2015, 117, 154902.
- 23 J. Chen and N. G. Park, Adv. Mater., 2019, 31, 1803019.
- 24 W. Jang, K. Kim, B. G. Kim, J. S. Nam, I. Jeon and D. H. Wang, Adv. Funct. Mater., 2022, 32, 2207713.
- 25 J. Yang, H. Zhang, H. Cui, S. Xu, G. Pan, H. Gao, Z. Zhang and Y. Mao, ACS Photonics, 2024, 11, 1181-1188.
- 26 V. M. Le Corre, M. B. Johnston, L. J. A. Koster, J. Lim and H. J. Snaith, Energy Environ. Sci., 2021, 15(17), 14006-14760.
- 27 Z. Y. Yin, Y. Chen, Y. Y. Zhang, Y. Yuan, Q. Yang, Y. N. Zhong, X. Gao, J. Xiao, Z. K. Wang, J. L. Xu and S. D. Wang, Adv. Funct. Mater., 2023, 33, 2302199.
- 28 O. D. I. Moseley, B. Roose, S. J. Zelewski and S. D. Stranks, ACS Appl. Energy Mater., 2023, 6, 10233-10242.
- 29 R. Ollearo, J. Wang, M. J. Dyson, C. H. L. Weijtens, M. Fattori, B. T. van Gorkom, A. J. J. M. van Breemen, S. C. J. Meskers, R. A. J. Janssen and G. H. Gelinck, Nat. Commun., 2021, 12, 7277.

- 30 O. Almora, D. Miravet, I. Gelmetti and G. Garcia-Belmonte, Phys. Status Solidi RRL, 2022, 16, 2200336.
- 31 B. R. Sutherland, A. K. Johnston, A. H. Ip, J. Xu, V. Adinolfi, P. Kanjanaboos and E. H. Sargent, ACS Photonics, 2015, 2, 1117-1123.
- 32 E. A. Duijnstee, V. M. Le Corre, M. B. Johnston, L. J. A. Koster, J. Lim and H. J. Snaith, Phys. Rev. Appl., 2021, **15**, 014006.
- 33 A. Datta, J. Fiala, P. Becla and S. Motakef, APL Mater., 2017, 5, 106109.
- 34 K. T. Ho, S. F. Leung, T. Y. Li, P. Maity, B. Cheng, H. C. Fu, O. F. Mohammed and J. H. He, Adv. Mater., 2018, 30, 1804372.
- 35 T. S. Ripolles, A. K. Baranwal, K. Nishinaka, Y. Ogomi, G. Garcia-Belmonte and S. Hayase, Phys. Chem. Chem. Phys., 2016, 18, 14970-14975.
- 36 Y. Shao, Y. Fang, T. Li, Q. Wang, Q. Dong, Y. Deng, Y. Yuan, H. Wei, M. Wang, A. Gruverman, J. Shield, J. Huang and L. N. U. S. Univ. Of Nebraska, Energy Environ. Sci., 2016, 9, 1752-1759.
- 37 S. E. J. O'Kane, G. Richardson, A. Pockett, R. G. Niemann, J. M. Cave, N. Sakai, G. E. Eperon, H. J. Snaith, J. M. Foster, P. J. Cameron and A. B. Walker, J. Mater. Chem. C, 2017, 5, 452-462.
- 38 T. Y. Yang, G. Gregori, N. Pellet, M. Gratzel and J. Maier, Angew. Chem., Int. Ed., 2015, 54, 7905-7910.
- 39 M. García-Batlle, S. Deumel, J. E. Huerdler, S. F. Tedde, O. Almora and G. Garcia-Belmonte, Adv. Photonics Res., 2022, 3, 2200136.
- 40 Y. Yun, G. S. Han, G. N. Park, J. Kim, J. Park, D. Vidyasagar, J. Jung, W. C. Choi, Y. J. Choi, K. Heo, J. Kang, J. S. Park, H. S. Jung and S. Lee, Adv. Mater., 2022, 34, 2206932.
- 41 Y. Liu, Y. Zhang, X. Zhu, J. Feng, I. Spanopoulos, W. Ke, Y. He, X. Ren, Z. Yang, F. Xiao, K. Zhao, M. Kanatzidis and S. F. Liu, Adv. Mater., 2021, 33, 2006010.
- 42 F. Furlan, D. Nodari, E. Palladino, E. Angela, L. Mohan, J. Briscoe, M. J. Fuchter, T. J. Macdonald, G. Grancini, M. A. Mclachlan and N. Gasparini, Adv. Opt. Mater., 2022, 10, 2201816.
- 43 L. Li, F. Zhang, S. Ye, X. Peng, Z. Sun, J. Lian, L. Liu, J. Qu and J. Song, Nano Energy, 2020, 71, 104611.
- 44 Y. Wang, D. Yang, D. Ma, D. H. Kim, T. Ahamad, S. M. Alshehri and A. Vadim, Sci. China: Mater., 2019, 62, 790-796.
- 45 D. Liu, B. Yu, M. Liao, Z. Jin, L. Zhou, X. Zhang, F. Wang, H. He, T. Gatti and Z. He, ACS Appl. Mater. Interfaces, 2020, 12, 30530-30537.
- 46 F. Yao, P. Gui, C. Chen, B. Li, R. Li, C. Tao, Q. Lin and G. Fang, ACS Appl. Mater. Interfaces, 2019, 11, 39875-39881.
- 47 E. Hong, D. Nodari, F. Furlan, E. Angela, J. Panidi, M. A. Mclachlan and N. Gasparini, Adv. Opt. Mater., 2024, 12, 2302712.
- 48 N. R. Al Amin, C. Lee, Y. Huang, C. Shih, R. Estrada, S. Biring, M. Kuo, C. Li, Y. Huang and S. Liu, ACS Appl. Mater. Interfaces, 2023, 15, 21284-21295.
- 49 Y. Yun, H. Cho, J. Jung, S. W. Yang, D. Vidyasagar, R. K. Gunasekaran and S. Lee, J. Mater. Sci. Technol., 2023, 152, 100-108.

- 50 J. Wu, L. Wang, A. Feng, S. Yang, N. Li, X. Jiang, N. Liu, S. Xie, X. Guo, Y. Fang, Z. Chen, D. Yang and X. Tao, *Adv. Funct. Mater.*, 2022, 32, 2109149.
- 51 P. Gui, J. Li, X. Zheng, H. Wang, F. Yao, X. Hu, Y. Liu and G. Fang, *J. Mater. Chem. C*, 2020, **8**, 684–6812.
- 52 W. Wang, D. Zhao, F. Zhang, L. Li, M. Du, C. Wang, Y. Yu, Q. Huang, M. Zhang, L. Li, J. Miao, Z. Lou, G. Shen, Y. Fang and Y. Yan, *Adv. Funct. Mater.*, 2017, 27, 1703953.
- 53 D. Luo, T. Zou, W. Yang, B. Xiang, X. Yang, Y. Wang, R. Su, L. Zhao, R. Zhu, H. Zhou, T. P. Russell, H. Yu and Z. H. Lu, *Adv. Funct. Mater.*, 2020, 30, 2001692.
- 54 Y. Zhao, C. Li, J. Jiang, B. Wang and L. Shen, *Small*, 2020, 16, 2001534.
- 55 S. Wang, M. Li, C. Song, C. Zheng, J. Li, Z. Li, Y. Zhang and J. Yao, *Appl. Surf. Sci.*, 2023, **623**, 156983.
- 56 Y. Miao, J. Wu, X. Qi, L. Yang, X. Wang, F. Zheng, F. Zhao, S. Shafique, Y. Zhu and Z. Hu, *Nano Energy*, 2023, 113, 108605.
- 57 J. Peng, Y. Xu, F. Yao, H. Huang, R. Li and Q. Lin, *Matter*, 2022, 5, 2251–2264.
- 58 L. Guo, Y. Qi, Z. Wu, X. Yang, G. Yan, R. Cong, L. Zhao, W. Zhang, S. Wang, C. Pan and Z. Yang, *Adv. Mater.*, 2023, 35, 2301705.
- 59 D. S. Lee, J. H. Heo, J. K. Park, B. W. Kim, H. J. Lee, Y. M. Song and S. H. Im, ACS Appl. Mater. Interfaces, 2021, 13, 16775–16783.
- 60 F. Zhu, G. Lian, B. Yu, T. Zhang, L. Zhang, H. Yu, D. Cui, Q. Wang, H. Zhang, Q. Meng and C. Wong, ACS Appl. Mater. Interfaces, 2022, 14, 1526–1536.
- 61 R. Ollearo, A. Caiazzo, J. Li, M. Fattori, A. J. J. M. van Breemen, M. M. Wienk, G. H. Gelinck and R. A. J. Janssen, *Adv. Mater.*, 2022, **34**, 2205261.
- 62 J. W. Lim, H. Wang, C. H. Choi, H. Kwon, L. N. Quan, W. Park, Y. Noh and D. H. Kim, *Nano Energy*, 2019, 57, 761–770.
- 63 H. Tsai, S. Shrestha, L. Pan, H. H. Huang, J. Strzalka, D. Williams, L. Wang, L. R. Cao and W. Nie, Adv. Mater., 2022, 34, 2106498.
- 64 R. Li, Y. Xu, W. Li, Y. Li, J. Peng, M. Xu and Q. Lin, *J. Phys. Chem. Lett.*, 2021, **12**, 1726–1733.
- 65 X. He, M. Xia, H. Wu, X. Du, Z. Song, S. Zhao, X. Chen, G. Niu and J. Tang, Adv. Funct. Mater., 2022, 32, 2109458.
- 66 Z. Liao, L. Qiu, T. Chen, W. Qian, Y. Wang, S. Yang, T. Sun, G. Yang, A. K. Srivastava and H. Zhou, Adv. Mater. Technol., 2023, 8, 2300714.
- 67 L. Min, W. Tian, F. Cao, J. Guo and L. Li, *Adv. Mater.*, 2021, 33, 2101714.
- 68 B. Jiang, G. Yan, Y. Xiao, Y. Yuan, C. Zhao, W. Mai and R. Hong, J. Mater. Sci., 2023, 58, 7076–7091.
- 69 Y. Hsiao, J. Song, H. Wu, K. Hong, C. Leu and C. Shih, J. Alloys Compd., 2021, 889, 161621.
- 70 X. Zhao, Y. Wang, L. Li, L. Huang, G. Li and W. H. Sun, J. Mater. Sci., 2021, 56, 9242–9253.
- 71 Z. Yang, M. Wang, J. Li, J. Dou, H. Qiu and J. Shao, *ACS Appl. Mater. Interfaces*, 2018, **10**, 26387–26395.

- 72 H. L. Zhu, H. Lin, Z. Song, Z. Wang, F. Ye, H. Zhang, W. Yin, Y. Yan and W. C. H. Choy, ACS Nano, 2019, 13, 11800–11808.
- 73 W. Li, Y. Xu, J. Peng, R. Li, J. Song, H. Huang, L. Cui and Q. Lin, ACS Appl. Mater. Interfaces, 2021, 13, 2971–2978.
- 74 C. Bao, Z. Chen, Y. Fang, H. Wei, Y. Deng, X. Xiao, L. Li and J. Huang, *Adv. Mater.*, 2017, 29, 1703209.
- 75 V. O. Eze, G. R. Adams, L. Braga Carani, R. J. Simpson and O. I. Okoli, *J. Phys. Chem. C*, 2020, **124**, 20643–20653.
- 76 M. Sulaman, S. Y. Yang, Z. H. Zhang, A. Imran, A. Bukhtiar, Z. H. Ge, Y. Tang, Y. R. Jiang, L. B. Tang and B. S. Zou, *Mater. Today Phys.*, 2022, 27, 100829.
- 77 Y. Zhao, S. Jiao, S. Liu, Y. Jin, S. Yang, X. Wang, T. Liu, H. Jin, D. Wang, S. Gao and J. Wang, *J. Alloys Compd.*, 2023, 965, 171434.
- 78 R. Xing, Z. Li, W. Zhao, D. Wang, R. Xie, Y. Chen, L. Wu and X. Fang, *Adv. Mater.*, 2024, **36**, 2310248.
- 79 Z. Shuang, H. Zhou, D. Wu, X. Zhang, B. Xiao, G. Ma, J. Zhang and H. Wang, *Chem. Eng. J.*, 2022, 433, 134544.
- 80 A. A. Khan, N. Kumar, U. Jung, W. Heo, Z. Tan and J. Park, *Nanoscale Horiz.*, 2023, **8**, 1577–1587.
- 81 Y. Yan, Q. Wu, Y. Zhao, S. Chen, S. Hu, J. Zhu, J. Huang and Z. Liang, *Small*, 2018, **14**, 1802764.
- 82 H. Di, W. Zeng, B. H. Li, F. Liao, C. Zhao, C. Liang, H. Li, J. C. Wang, D. B. Cheng, Z. Ren and Y. Zhao, *Adv. Sci.*, 2023, 10, 2302917.
- 83 L. He, G. Hu, J. Jiang, W. Wei, X. Xue, K. Fan, H. Huang and L. Shen, *Adv. Mater.*, 2023, 35, 2210016.
- 84 Z. Gao, Y. Zheng, G. Huang, G. Yang, X. Yu and J. Yu, *Micromachines*, 2020, 11, 1090.
- 85 D. Zhang, H. Wei and L. Zhu, Org. Electron., 2023, 114, 106726.
- 86 M. Xia, Z. Song, H. Wu, X. Du, X. He, J. Pang, H. Luo, L. Jin, G. Li, G. Niu and J. Tang, Adv. Funct. Mater., 2022, 32, 2110729.
- 87 H. Zhou, R. Wang, X. Zhang, B. Xiao, Z. Shuang, D. Wu and P. Qin, *Chem. Commun.*, 2023, 59, 8544–8547.
- 88 L. Jiang, Z. Li, Q. Dong, X. Rong and G. Dong, *ACS Appl. Mater. Interfaces*, 2023, **15**, 32647–32655.
- 89 X. Xu, C. C. Chueh, P. Jing, Z. Yang, X. Shi, T. Zhao, L. Y. Lin and A. K. Y. Jen, *Adv. Funct. Mater.*, 2017, 27, 1701053.
- 90 S. Wang, T. Li, Q. Li, H. Zhao, C. Zheng, M. Li, J. Li, Y. Zhang and J. Yao, J. Mater. Chem. C, 2022, 10, 7886–7895.
- 91 F. Liu, K. Liu, S. Rafique, Z. Xu, W. Niu, X. Li, Y. Wang, L. Deng, J. Wang, X. Yue, T. Li, J. Wang, P. Ayala, C. Cong, Y. Qin, A. Yu, N. Chi and Y. Zhan, *Adv. Sci.*, 2023, 10, 2205879.
- 92 J. H. Lu, M. T. Cheng, H. L. Hsu, S. W. Liu and C. P. Chen, *Adv. Funct. Mater.*, 2020, **30**, 2002503.
- 93 R. Li, J. Peng, Y. Xu, W. Li, L. Cui, Y. Li and Q. Lin, *Adv. Opt. Mater.*, 2021, **9**, 2001587.
- 94 Y. Wang, S. Ye, Z. Sun, J. Zhu, Y. Liu, R. Wang, F. Lin, W. Zhang, Y. Yang and C. Wang, ACS Appl. Mater. Interfaces, 2023, 15, 59005–59015.

- 95 Z. Gao, H. Zhou, K. Dong, C. Wang, J. Wei, Z. Li, J. Li, Y. Liu, J. Zhao and G. Fang, Nano-Micro Lett., 2022, 14, 215.
- 96 Z. Jia, J. Peng, L. Yu, T. Jiang, Y. Li, F. Yao, F. Ren and Q. Lin, Chem. Eng. J., 2022, 450, 138229.
- 97 H. Zhao, T. Li, J. Li, Q. Li, S. Wang, C. Zheng, J. Li, M. Li, Y. Zhang and J. Yao, J. Alloys Compd., 2022, 908, 164482.
- 98 J. Li, J. Ran, Z. Uddin, J. Li, F. Wan, Y. Yuan, J. Chen and B. Yang, ACS Appl. Energy Mater., 2022, 5, 12158-12164.
- 99 B. Jo, K. M. Kim, S. Lee, H. J. Kim, J. Kim, J. Kang, G. Namkoong, G. S. Han and H. S. Jung, Chem. Mater., 2023, 35, 10495-10503.
- 100 H. Liu, L. Zhu, H. Zhang, X. He, F. Yan, K. S. Wong and W. C. H. Choy, ACS Energy Lett., 2023, 8, 577-589.
- 101 W. Kim, J. Park, Y. Aggarwal, S. Sharma, E. H. Choi and B. Park, Nanomaterials, 2023, 13, 619.
- 102 N. Ma, J. Jiang, Y. Zhao, L. He, Y. Ma, H. Wang, L. Zhang, C. Shan, L. Shen and W. Hu, Nano Energy, 2021, 86, 106113.
- 103 Y. Aggarwal, J. Park, W. Kim, S. Sharma, H. Jeong, M. G. Kim, J. Kil, E. H. Choi and B. Park, Sol. Energy Mater. Sol. Cells, 2024, 270, 112815.
- 104 M. Wang, H. Sun, F. Cao, W. Tian and L. Li, Adv. Mater., 2021, 33, 2100625.
- 105 Q. Lin, A. Armin, D. M. Lyons, P. L. Burn and P. Meredith, Adv. Mater., 2015, 27, 2060-2064.
- 106 C. Bao, J. Yang, S. Bai, W. Xu, Z. Yan, Q. Xu, J. Liu, W. Zhang and F. Gao, Adv. Mater., 2018, 30, 1803422.
- 107 G. Cen, Y. Liu, C. Zhao, G. Wang, Y. Fu, G. Yan, Y. Yuan, C. Su, Z. Zhao and W. Mai, Small, 2019, 15, 1902135.
- 108 S. Demchyshyn, M. Verdi, L. Basiricò, A. Ciavatti, Hailegnaw, D. Cavalcoli, Μ. C. Scharber, N. S. Sariciftci, M. Kaltenbrunner and B. Fraboni, Adv. Sci., 2020, 7, 2002586.
- 109 X. Zhang, Z. Li, T. Yan, L. Su and X. Fang, Small, 2023, 19, 2206310.
- 110 J. Y. Chun, B. G. Kim, J. Y. Kim, W. Jang and D. H. Wang, Carbon Energy, 2023, 5, e350.
- 111 C. Li, J. Lu, Y. Zhao, L. Sun, G. Wang, Y. Ma, S. Zhang, J. Zhou, L. Shen and W. Huang, Small, 2019, 15, 1903599.
- 112 W. Wei, Y. Zhang, Q. Xu, H. Wei, Y. Fang, Q. Wang, Y. Deng, T. Li, A. Gruverman, L. Cao and J. Huang, Nat. Photonics, 2017, 11, 315-321.
- 113 H. L. Zhu, J. Cheng, D. Zhang, C. Liang, C. J. Reckmeier, H. Huang, A. L. Rogach and W. C. H. Choy, ACS Nano, 2016, 10, 6808-6815.
- 114 B. Pan, M. Wu, G. Yang, D. Zhao and J. Yu, Opt. Lett., 2020, **45**, 5860-5863.
- 115 Z. Liu, Z. Zhang, X. Zhang, X. Li, Z. Liu, G. Liao, Y. Shen and M. Wang, Nano Lett., 2023, 23, 1181-1188.
- 116 Z. Chen, H. Wang, F. Li, W. Zhang, Y. Shao and S. Yang, ACS Appl. Mater. Interfaces, 2023, 15, 51370-51379.
- 117 L. He, M. Li, Q. Chen, R. Sun, F. Wang, X. Wang, H. Wu, W. Wei, T. Qin and L. Shen, ACS Appl. Mater. Interfaces, 2022, 14, 46809-46818.
- 118 G. Li, Y. Wang, L. Huang and W. Sun, J. Alloys Compd., 2022, 907, 164432.

- 119 M. Sulaman, Y. Song, S. Yang, M. I. Saleem, M. Li, C. Perumal Veeramalai, R. Zhi, Y. Jiang, Y. Cui, Q. Hao and B. Zou, ACS Appl. Mater. Interfaces, 2020, 12, 26153-26160.
- 120 D. H. Shin, S. H. Shin and S. Choi, Appl. Surf. Sci., 2020, **514**, 145880.
- 121 L. He, D. Wang, Y. Zhao, Y. Zhang, W. Wei and L. Shen, J. Mater. Chem. C, 2021, 9, 11722-11728.
- 122 C. Shan, F. Meng, J. Yu, Z. Wang, W. Li, D. Fan, R. Chen, H. Ma, G. Li and A. K. K. Kyaw, J. Mater. Chem. C, 2021, 9, 7632-7642.
- 123 J. Yang, Y. Wang, L. Huang, G. Li, X. Qiu, X. Zhang and W. Sun, J. Phys. Chem. Lett., 2022, 13, 3904-3914.
- 124 J. Park, Y. Aggarwal, W. Kim, S. Sharma, E. H. Choi and B. Park, Opt. Express, 2023, 31, 1202.
- 125 L. Dou, Y. Yang, J. You, Z. Hong, W. Chang, G. Li and Y. Yang, Nat. Commun., 2014, 5, 5404.
- 126 L. Huang, Y. Wang, X. Zhu, X. Zhao, G. Li, L. Li and W. Sun, J. Phys. Chem. C, 2021, 125, 16066-16074.
- 127 R. Guo, F. Huang, K. Zheng, T. Pullerits and J. Tian, ACS Appl. Mater. Interfaces, 2018, 10, 35656-35663.
- 128 A. M. Afzal, I. G. Bae, Y. Aggarwal, J. Park, H. R. Jeong, E. H. Choi and B. Park, Sci. Rep., 2021, 11, 169.
- 129 B. Li, X. Huang, X. Wu, Q. Zuo, Y. Cao, Q. Zhu, Y. Li, Y. Xu, G. Zheng, D. Chen, X. H. Zhu, F. Huang, H. Zhen, L. Hou, J. Qing and W. Cai, Adv. Funct. Mater., 2023, 33, 2300216.
- 130 Y. Subramaniam and K. L. Woon, Synth. Met., 2023, 293, 117261.
- 131 Y. Liu and Z. Ji, Appl. Phys. Lett., 2023, 122, 21103.
- 132 Y. Wang, X. Zhang, Q. Jiang, H. Liu, D. Wang, J. Meng, J. You and Z. Yin, ACS Appl. Mater. Interfaces, 2018, 10, 6505-6512.
- 133 Y. Yuan, Z. Ji, G. Yan, Z. Li, J. Li, M. Kuang, B. Jiang, L. Zeng, L. Pan and W. Mai, J. Mater. Sci. Technol., 2021, 75, 39-47.
- 134 J. Lin, F. Hsu, C. Chang and Y. Chen, J. Mater. Chem. C, 2021, 9, 5190-5197.
- 135 T. Sun, T. Chen, J. Chen, Q. Lou, Z. Liang, G. Li, X. Lin, G. Yang and H. Zhou, Nanoscale, 2023, 15, 783-7811.
- 136 F. Tang, Q. Chen, L. Chen, F. Ye, J. Cai and L. Chen, Appl. Phys. Lett., 2016, 109, 123301.
- 137 T. Zou, J. Zhang, S. Huang, C. Liu, R. Qiu, X. Wang, W. Wu, H. Wang, Z. Wei, Q. Dai, C. Liu, S. Zhang and H. Zhou, RSC *Adv.*, 2019, **9**, 3800-3808.
- 138 Z. Ji, G. Cen, C. Su, Y. Liu, Z. Zhao, C. Zhao and W. Mai, Adv. Opt. Mater., 2020, 8, 2001436.
- 139 H. Mescher, F. Schackmar, H. Eggers, T. Abzieher, M. Zuber, E. Hamann, T. Baumbach, B. S. Richards, G. Hernandez-Sosa, U. W. Paetzold and U. Lemmer, ACS Appl. Mater. Interfaces, 2020, 12, 15774-15784.
- 140 C. Liu, K. Wang, C. Yi, X. Shi, P. Du, A. W. Smith, A. Karim and X. Gong, J. Mater. Chem. C, 2015, 3, 66-666.
- 141 Z. Ji, Y. Liu, W. Li, C. Zhao and W. Mai, Sci. Bull., 2020, 65, 1371-1379.
- 142 K. M. Sim, A. Swarnkar, A. Nag and D. S. Chung, Laser Photonics Rev., 2018, 12, 1700209.

- 143 T. Ji, H. Zhang, J. Guo, Y. Wang, L. Shi, Y. Wu, W. Wang, G. Li, R. Wen, L. Xiao, Q. Su, B. Xu, H. Chen and Y. Cui, Adv. Funct. Mater., 2023, 33, 2210548.
- 144 M. Long, L. Yang, D. An, J. Dai, Y. Wang and X. Yao, Opt. Mater., 2024, 147, 114652.
- 145 C. A. R. Perini, A. J. Barker, M. Sala, A. Petrozza and M. Caironi, *Semicond. Sci. Tech.*, 2018, 33, 94004.
- 146 B. Bhardwaj, U. Bothra, S. Singh, S. Mills, T. J. Ronningen, S. Krishna and D. Kabra, Appl. Phys. Rev., 2023, 10, 21419.
- 147 X. Zhu, Y. Liu, S. Huang, X. Gao, J. Li, H. Sun, P. Wangyang and X. Niu, ACS Appl. Mater. Interfaces, 2024, 16(13), 16474.
- 148 X. Zhang, D. Chu, B. Jia, Z. Zhao, J. Pi, Z. Yang, Y. Li, J. Hao, R. Shi, X. Dong, Y. Liang, J. Feng, A. Najar, Y. Liu and S. F. Liu, *Adv. Mater.*, 2024, 36, 2305513.
- 149 S. Liu, Y. Chen, W. Gao, W. Li, X. Yang, Z. Li, Z. Xiao, Y. Liu and Y. Wang, *Adv. Mater.*, 2023, 35, 2303544.
- 150 X. Wang, Y. Xu, Y. Pan, Y. Li, J. Xu, J. Chen, J. Wu, Q. Li, X. Zhang, Z. Zhao, C. Li, E. E. Elemike, D. C. Onwudiwe, J. Akram and W. Lei, *Nano Energy*, 2021, 89, 106311.
- 151 C. Zou, D. Yu, M. Lin, B. Shen, Y. Peng, Y. Zheng, H. G. Yang, Y. Hou and S. Yang, *Adv. Funct. Mater.*, 2024, 2316430.
- 152 Q. Lin, Z. Wang, M. Young, J. B. Patel, R. L. Milot, L. Martinez Maestro, R. R. Lunt, H. J. Snaith, M. B. Johnston and L. M. Herz, Adv. Funct. Mater., 2017, 27, 1702485.
- 153 R. Guo, C. Bao, F. Gao and J. Tian, Adv. Opt. Mater., 2020, 8, 2000557.
- 154 S. Liu, S. Jiao, H. Lu, Y. Nie, S. Gao, D. Wang, J. Wang and L. Zhao, *J. Alloys Compd.*, 2022, **890**, 161827.
- D. Shao, W. Zhu, G. Xin, X. Liu, T. Wang, S. Shi, J. Lian and
   Sawyer, J. Mater. Chem. C, 2020, 8, 1819–1825.
- 156 L. Li, Y. Li, J. Li, Y. Fang and D. Yang, *Adv. Opt. Mater.*, 2023, **11**, 2202276.
- 157 S. Yin, Y. Cheng, Y. Li, W. Liang, T. Li, J. Ma, D. Wu, Z. Shi and X. Li, *J. Mater. Sci.*, 2021, **56**, 13633–13645.
- 158 J. Zhao, X. Wang, Y. Pan, Y. Xu, Y. Li, J. Chen, J. Wu, Q. Li, Z. Zhao, X. Zhang, J. Akram, B. S. Bae, H. Yang and W. Lei, *Front. Phys.*, 2021, 9, 712316.
- 159 Y. Pan, X. Wang, J. Zhao, Y. Xu, Y. Li, Q. Li, X. Zhang, Z. Zhao, Z. Zhu, C. Jing, W. Jun, E. Emeka Elemike, B. S. Bae and W. Lei, *CrystEngComm*, 2021, 23, 4954–4962.
- 160 Y. Liu, Y. Gao, J. Zhi, R. Huang, W. Li, X. Huang, G. Yan,Z. Ji and W. Mai, *Nano Res.*, 2022, 15, 1094–1101.
- 161 F. Zhao, K. Xu, X. Luo, Y. Liang, Y. Peng and F. Lu, Adv. Opt. Mater., 2018, 6, 1700509.
- 162 V. Anilkumar, A. Mahapatra, J. Nawrocki, R. D. Chavan, P. Yadav and D. Prochowicz, Adv. Opt. Mater., 2024, 12, 2302032.
- 163 Y. Pan, X. Wang, Y. Xu, Y. Li, E. E. Elemike, A. Shuja, Q. Li, X. Zhang, J. Chen, Z. Zhao and W. Lei, *Front. Chem.*, 2020, 8, 791.
- 164 W. Qu, S. Weng, L. Zhang, M. Sun, B. Liu, W. Du and Y. Zhang, *Appl. Phys. Express*, 2020, **13**, 121001.

- 165 L. Cui, J. Peng, W. Li, Y. Xu, M. Zheng and Q. Lin, *Phys. Status Solidi R*, 2020, 14, 1900653.
- 166 T. Zhu, L. Shen, D. Zhang, J. Zheng and X. Gong, ACS Appl. Mater. Interfaces, 2022, 14, 18744–18750.
- 167 H. Zhou, Z. Song, P. Tao, H. Lei, P. Gui, J. Mei, H. Wang and G. Fang, *RSC Adv.*, 2016, **6**, 625–628.
- 168 J. Wang, J. Li, S. Lan, C. Fang, H. Shen, Q. Xiong and D. Li, ACS Nano, 2019, 13, 5473–5484.
- 169 V. Manjunath, P. K. Mishra, R. Dobhal, S. Bimli, P. M. Shirage, S. Sen, P. A. Shaikh and R. S. Devan, ACS Appl. Electron. Mater., 2021, 3, 4548–4557.
- 170 Z. Li, Y. Liu, J. He, G. Yan, G. Cen, B. Jiang, C. Zhao, Y. Yuan and W. Mai, Surf. Interfaces, 2022, 29, 101705.
- 171 L. Shen, Y. Lin, C. Bao, Y. Bai, Y. Deng, M. Wang, T. Li, Y. Lu, A. Gruverman, W. Li and J. Huang, *Mater. Horiz.*, 2017, 4, 242–248.
- 172 Z. Qin, D. Song, Z. Xu, B. Qiao, D. Huang and S. Zhao, *Org. Electron.*, 2020, **76**, 105417.
- 173 F. Cui, P. Zhang, L. Zhang, Y. Hua, X. Sun, X. Li, G. Zhang and X. Tao, *Chem. Mater.*, 2022, **34**, 9601–9612.
- 174 C. Liu, H. Chen, P. Lin, H. Hu, Q. Meng, L. Xu, P. Wang, X. Wu and C. Cui, *J. Phys.: Condens. Matter.*, 2022, 34, 405703.
- 175 W. Li, L. Liu, M. Tan, Y. He, C. Guo, H. Zhang, H. Wei and B. Yang, *Adv. Funct. Mater.*, 2021, 31, 2107843.
- 176 Y. Zhou, L. Zhao, Z. Ni, S. Xu, J. Zhao, X. Xiao and J. Huang, *Sci. Adv.*, 2021, 7, eabg6716.
- 177 Y. Wang, D. Yang, X. Zhou, D. Ma, A. Vadim, T. Ahamad and S. M. Alshehri, Adv. Opt. Mater., 2017, 5, 1700213.
- 178 C. W. Jang, D. H. Shin and S. Choi, *J. Alloys Compd.*, 2023, **948**, 169716.
- 179 D. Zhao, Y. Wang, X. Sun, X. Wu, B. Li, S. Zhang, D. Gao,
  B. Liu, S. Gong, Z. Li, C. Zhang, X. Chen, S. Xiao, S. Yang,
  Z. Li and Z. Zhu, *Small*, 2023, 2309827.
- 180 Y. Song, L. Li, M. Hao, W. Bi, A. Wang, Y. Kang, H. Li, X. Li, Y. Fang, D. Yang and Q. Dong, *Adv. Mater.*, 2021, 33, 2103078.
- 181 P. Jin, Y. Tang, D. Li, Y. Wang, P. Ran, C. Zhou, Y. Yuan, W. Zhu, T. Liu, K. Liang, C. Kuang, X. Liu, B. Zhu and Y. M. Yang, *Nat. Commun.*, 2023, 14, 626.
- 182 Z. Zhan, D. Lin, J. Cai, Y. Lu, A. Chen, T. Zhang, K. Chen, P. Liu, X. Wang and W. Xie, *Adv. Mater.*, 2022, 34, 2207106.
- 183 L. Wang, X. Zou, J. Lin, J. Jiang, Y. Liu, X. Liu, X. Zhao, Y. F. Liu, J. C. Ho and L. Liao, ACS Nano, 2019, 13, 4804–4813.
- 184 C. Y. Wu, W. Peng, T. Fang, B. Wang, C. Xie, L. Wang, W. H. Yang and L. B. Luo, *Adv. Electron. Mater.*, 2019, 5, 1900135.
- 185 L. Martínez Goyeneche, L. Gil Escrig, I. Susic, D. Tordera, H. J. Bolink and M. Sessolo, *Adv. Opt. Mater.*, 2022, **10**, 2201047.
- 186 G. Cen, Y. Lv, Y. Yuan, G. Yan, Z. Ji, C. Zhao and W. Mai, *J. Mater. Chem. C*, 2023, **11**, 9341–9347.

- 187 Y. Zhou, X. Qiu, Z. A. Wan, Z. Long, S. Poddar, Q. Zhang, Y. Ding, C. L. J. Chan, D. Zhang, K. Zhou, Y. Lin and Z. Fan, Nano Energy, 2022, **100**, 107516.
- 188 L. Li, H. Chen, Z. Fang, X. Meng, C. Zuo, M. Lv, Y. Tian, Y. Fang, Z. Xiao, C. Shan, Z. Xiao, Z. Jin, G. Shen, L. Shen and L. Ding, Adv. Mater., 2020, 32, 1907257.
- 189 F. Wang, T. Zhang, R. Xie, Z. Wang and W. Hu, Nat. Commun., 2023, 14, 2224.
- 190 Y. Fang, A. Armin, P. Meredith and J. Huang, Nat. Photonics, 2019, 13, 1-4.
- 191 Y. Haruta, P. Huber, A. Hart, M. Bazalova-Carter and M. I. Saidaminov, ACS Energy Lett., 2024, 9,
- 192 H. T. Chandran, S. Mahadevan, R. Ma, Y. Tang, T. Zhu, F. Zhu, S. Tsang and G. Li, Appl. Phys. Lett., 2024, **124**, 101113.