Materials Advances



PAPER View Article Online



Cite this: *Mater. Adv.*, 2021, **2** 1320

Received 28th October 2020, Accepted 7th January 2021

DOI: 10.1039/d0ma00845a

rsc.li/materials-advances

Alkylamine screening and zinc doping of highly luminescent 2D tin-halide perovskites for LED lighting†

Yao Liu,‡^a Aifei Wang, [b]‡§^a Jiajing Wu,^a Chuying Wang,^a Ziliang Li,^b Guangcai Hu,^a Shigi Sui, [b]^a Jia-Xin She,^c Wen Meng,^a Weigiang Li [b]^c and Zhengtao Deng [b]*^a

In recent years, two-dimensional (2D) layered tin halide perovskites have attracted much attention due to their excellent luminescence properties compared with their three-dimensional (3D) analogs. Here, we synthesized 2D perovskites of the form (RNH₃)₂SnBr₄ through a facile hot-injection approach without the use of toxic tri-n-octylphosphine (TOP) as the solvent. We found that these compounds have strong photoluminescence (PL) emission with high PL quantum yields (QY) of 35% ((C₆H₁₃NH₃)₂SnBr₄), 82% ((C₈H₁₇NH₃)₂SnBr₄), 60% ((C₁₂H₂₅NH₃)₂SnBr₄) and 50% ((C₁₈H₃₅NH₃)₂SnBr₄). Among them, ((C₆H₁₃NH₃)₂SnBr₄) was synthesized for the first time; however, (C₁₈H₃₆NH₃)₂SnBr₄ perovskites showed the best stability with a PL QY decrease of less than 1% after 30 days under ambient air and humidity conditions. In addition, other 2D (C₈H₁₇NH₃)₂SnX₄ (X = Br, I, or mixture) perovskites were prepared by adjusting the halide ratio, resulting in spectral tunability from yellow to red. Interestingly, through Zn²⁺ doping, the morphology became more uniform, and the PL stability was significantly improved. Finally, we used Zn²⁺-doped (C₈H₁₇NH₃)₂SnBr₄ yellow phosphor to fabricate UV-pumped yellow LEDs. We expect these 2D perovskites to be promising phosphors in future solid-state lighting and display technologies.

Introduction

Lead halide perovskites (LHPs) have been used in many fields including light-emitting diode (LED) devices, solar cells^{2,3} and television displays due to their superior optical properties^{1,5} and low-cost preparation. Although many advances have been made in lead halide perovskites, their toxicity to humans and long-term pollution to the environment remain to be addressed. Thus, lead-free halide perovskites (LFHPs) with similar optoelectronic properties to LHPs have been broadly studied. Tin-halide perovskites have drawn a lot of attention for substitution of lead in all optoelectronic applications.

However, owing to the lack of an inert pair effect as in Pb²⁺, divalent Sn is easily oxidized from the +2 to +4 state, causing deep defects in perovskites. The instability of tin-halide perovskites will seriously affect the device performance, even under trace amounts of water and oxygen in the glovebox. ^{18–20}

A series of strategies to overcome the instability of tin-halide perovskites have been developed. Deng et al. successfully synthesized Cs₂SnI₆ nanocrystals and applied them to fabricate field effect transistors (FETs) via direct replacement of Sn²⁺ with Sn^{4+,21} Bi-doped Cs₂SnCl₆ bulk crystals with a PL QY near 80% were reported to emit deep-blue light, which also showed improved stability.²² In addition to direct substitution of Sn²⁺, introducing hydrophobic organic molecules into the crystal structure is another way to protect Sn²⁺ from water and oxygen. Recently, two-dimensional (2D) layered tin-halide perovskites with the formula of $(R-NH_3)_2A_{n-1}Sn_nX_{3n+1}$ (R = alkyl chains; A = Cs⁺, MA⁺, FA⁺; X = Cl⁻, Br⁻, I⁻) have attracted much attention. 10,23 Such 2D tin-halide perovskites showed good photoluminescence and electroluminescence as well as improved resistance to air and moisture 10,15,24 compared with homologous three-dimensional (3D) ASnX₃ perovskites. For instance, 2D (PEA)2SnI4 thin films were reported to exhibit superior photoluminescence and air stability over bulk CH₃NH₃SnI₃ perovskites, which were used as emitting layers in

^a College of Engineering and Applied Sciences, Nanjing University, Nanjing, Jiangsu 210023, China. E-mail: dengz@nju.edu.cn

b Department of Electrical and Computer Engineering, University of Toronto, 10 King's College Road, Toronto, Ontario M5S 3G4, Canada


^c State Key Laboratory for Mineral Deposits Research, School of Earth Sciences and Engineering, Nanjing University, Nanjing, Jiangsu, 210023, P. R. China

 $[\]dagger$ Electronic supplementary information (ESI) available: Fig. S1–S12 and Tables S1–S3. CCDC. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0ma00845a

 $[\]ddagger$ These two authors contributed equally to this work.

[§] Current address: Institute of Advanced Materials (IAM), Nanjing Tech University (NJ Tech), 5 Xinmofan Road, Nanjing 210009, P. R. China.

Paper Materials Advances

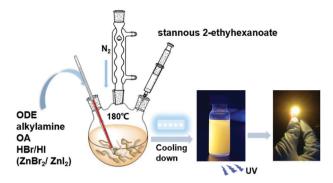

Scheme 1 Schematic diagram of the synthesis of the 2D $(RNH_3)_2SnX_4$ perovskites by a hot-injection method.

LEDs.²⁴ Ning's group reported hollow 2D layered (HMD)₃SnBr₈ crystals synthesized by the antisolvent method. These crystals showed bright yellow luminescence with a PL QY of 86% and were used to fabricate remarkably stable WLEDs by mixing with commercially blue phosphor.²⁵ A (C₁₈H₃₅NH₃)₂SnBr₄ 2D perovskite film was applied to produce orange LEDs, showing improved device performance than the 2D analogues, but the usage of toxic and expensive tri-*n*-octylphosphine (TOP) during the synthesis limited its large-scale application.²⁶ Recently, for the first time, our group synthesized highly emissive 2D tinhalide (OCTAm)₂SnX₄ perovskites, in aqueous solution with a PL QY near unity and high stability in air.²⁷ We noted that Li's group reported the facile synthesis of 2D bulk tin-halide (RNH₃)₂SnBr₄ perovskites and explored the effect of different carbon chains on 2D organic tin-halide perovskites.²⁸

The length of the organic amine chain will affect the transport of carriers, thereby affecting the device performance of 2D tin-halide perovskites.²⁹ Herein, we synthesized 2D (RNH₃)₂SnX₄ perovskites with high luminescence emission from yellow to red by a hot injection method. (RNH₃) represents the long-chain amine cation: hexylamine cation (C₆H₁₃NH₃⁺), octylamine cation $(C_8H_{17}NH_3^+)$, dodecylamine cation $(C_{12}H_{25}NH_3^+)$, and oleylamine cation $(C_{18}H_{35}NH_3^+)$. For simplicity, we use C6, C8, C12, and C18 to represent $(C_6H_{13}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2SnBr_4$, $(C_{12}H_{25}NH_3)_2SnBr_4$ and (C₁₈H₃₅NH₃)₂SnBr₄, respectively, in the figures. Compared with room-temperature synthesis, perovskites synthesized by the hot injection method were more stable.30 In addition, we thoroughly discussed the effects of A-site organic cation substitution on their structural and optical properties and stability. The spectral tunability of 2D tin hybrid perovskites by adjusting the Br/I halide ratio was also explored. Furthermore, Zn²⁺ was introduced as a dopant into the 2D $(C_8H_{17}NH_3)_2SnX_4$ (X = Br, I) perovskite lattice. Finally, we successfully used the Zn²⁺-doped (C₈H₁₇NH₃)₂SnBr₄ perovskite as a yellow phosphor to fabricate UV-pumped LEDs. In comparison to previous reports, the differences and significance of the current work are as follows: (i) we used stannous 2-ethylhexanoate instead of the commonly used TOP-SnBr2 in the high temperature reaction, which could avoid the problem of toxicity and high cost; (ii) all the (RNH₃)₂SnBr₄ samples showed bright emission from yellow to

orange and exhibited good air stability; (iii) by adjusting the Br/I ratio, the PL emission peak could be tuned from yellow to red; (iv) better morphology and stability were achieved after Zn^{2+} doping into 2D $(C_8H_{17}NH_3)_2SnX_4$ perovskites; (v) Zn^{2+} -doped $(C_8H_{17}NH_3)_2SnBr_4$ yellow phosphor with excellent optical properties was used to fabricate UV-pumped LEDs.

Results and discussion

We adopted a traditional hot-injection approach to synthesize the 2D (RNH₃)₂SnBr₄ perovskites without utilizing the toxic TOP solvent (details are shown in the Experimental section). Typically, oleic acid (OA), alkylamine, and hydrobromic acid (HBr) were dissolved in octadecene (ODE) to form a RNH₃⁺-halide-precursor solution; while the organic amine was partially protonated to RNH₃⁺ through acidification, the rest of the amine and OA molecules acted as dual ligands. After the stannous 2-ethylhexanoate was injected at elevated temperatures, the luminescent 2D (RNH₃)₂SnBr₄ perovskites were precipitated (Scheme 1).

All the as-synthesized $(RNH_3)_2SnBr_4$ perovskites showed periodic diffraction peaks in powder X-ray diffraction (PXRD) patterns (Fig. 1a), which were the characteristics of 2D perovskites. According to Bragg's law, the layer spacing of 2D $(RNH_3)_2SnBr_4$ perovskites was calculated as 18.1 Å $((C_6H_{13}NH_3)_2SnBr_4)$, 24.6 Å $((C_8H_{17}NH_3)_2SnBr_4)$, 33.8 Å $((C_{12}H_{25}NH_3)_2SnBr_4)$ and 39.6 Å $((C_{18}H_{35}NH_3)_2SnBr_4)$. The schematic diagrams of the crystal structures of 2D $(RNH_3)_2SnBr_4$ perovskites are shown in Fig. 1b. A single metal halide

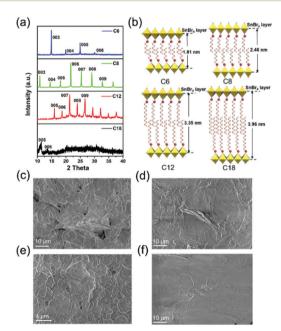


Fig. 1 (a) Powder X-ray diffraction (PXRD) patterns and (b) schematic diagrams of crystal structures for 2D (RNH₃)₂SnBr₄ perovskites. Scanning electron microscopy (SEM) images of 2D (RNH₃)₂SnBr₄ perovskites: (c) C6, (d) C8, (e) C12, and (f) C18 (for simplicity, we use C6, C8, C12, and C18 to represent $(C_6H_{13}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2SnBr_4$, $(C_{12}H_{25}NH_3)_2SnBr_4$, and $(C_{18}H_{35}NH_3)_2SnBr_4$ perovskites, respectively).

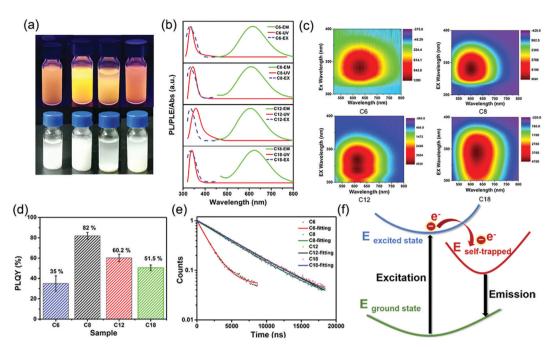


Fig. 2 Optical properties of 2D $(RNH_3)_2SnBr_4$ perovskites: (a) Photographs of the colloidal suspension at room temperature and under UV light. (b) UV-vis absorption, PL emission, and PL excitation spectra. (c) Three-dimensional excitation-emission matrix (EEM) fluorescence spectrum. (d) PL QY and (e) time-resolved PL decay spectra. (f) Schematic of exciton self-trapping in 2D $(RNH_3)_2SnBr_4$ perovskites (for simplicity, we use C6, C8, C12, and C18 to represent $(C_6H_{13}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2SnBr_4$, $(C_12H_{25}NH_3)_2SnBr_4$, and $(C_{18}H_{35}NH_3)_2SnBr_4$ perovskites, respectively).

octahedral layer is \sim 6.7 Å, so we can infer that two interleaving cation layers occupy spaces of \sim 11.4 Å ((C₆H₁₃NH₃)₂SnBr₄), \sim 17.9 Å ((C₈H₁₇NH₃)₂SnBr₄), \sim 27.1 Å ((C₁₂H₂₅NH₃)₂SnBr₄), and \sim 32.9 Å ((C₁₈H₃₅NH₃)₂SnBr₄).

Fourier-transform infrared (FTIR) spectroscopy (Fig. S1, ESI†) also proved that the NH₃⁺ characteristic peak at 3100 cm⁻¹ existed in all the 2D (RNH₃)₂SnBr₄ perovskites.^{33,34} X-Ray photoelectron spectroscopy (XPS) spectra of 2D (C₈H₁₇NH₃)₂SnBr₄ perovskites are shown in Fig. S2 (ESI†). An obvious peak at 284 eV was related to C 1s; the peak at 400.9 eV was attributed to N 1s; the peaks located at 485.8 eV and 494.1 eV originated from Sn 3d of Sn²⁺ ions;^{26,28} the peak located at 67.5 eV was attributed to Br 3d.35 According to the integrated peak intensities, the elemental N:Sn:Br ratio of the 2D (C₈H₁₇NH₃)₂SnBr₄ perovskites was 4.4:1:5.6. The total amount of nitrogen detected comes from alkylamine molecules from the perovskite structure and the surrounding organic protective shell.³⁶ 2D (RNH₃)₂SnBr₄ perovskites with layered morphology were observed in scanning electron microscopy (SEM) (Fig. 1c-f and Fig. S3, ESI†), which agreed well with the results of XRD (Fig. 1a). The elements of nitrogen, tin, and bromide were distributed homogeneously in all the samples (Fig. S4, ESI†). The TEM and HAADF-STEM images in Fig. S5 (ESI†) also indicated the 2D layered structure of (C₁₈H₃₅NH₃)₂SnBr₄ perovskites. The colloidal suspension of 2D (RNH₃)₂SnBr₄ perovskites in hexane showed yellow to orange emission under 365 nm UV light as the alkylammonium ligand varies, among which the (C₈H₁₇NH₃)₂SnBr₄ perovskites showed the strongest luminescence (Fig. 2a). The UV-vis absorption, PL excitation, and PL emission spectra of these (RNH₃)₂SnBr₄ perovskites are shown in Fig. 2b. (RNH₃)₂SnBr₄ perovskites with different alkylammonium cations showed absorption and PL peaks at different wavelengths, as summarized in Table 1. All these perovskites show broadband emission with extremely large full width at half maximum (FWHM) (134-138 nm). The $[F(R)h\nu]^2$ versus energy curves are shown in Fig. S6 (ESI†), showing that 2D (RNH₃)₂SnBr₄ perovskites possess direct band gaps of 3.48 eV ((C₆H₁₃NH₃)₂SnBr₄), 3.38 eV $((C_8H_{17}NH_3)_2SnBr_4)$, 3.20 eV $((C_{12}H_{25}NH_3)_2SnBr_4)$ and 3.36 eV ((C₁₈H₃₆NH₃)₂SnBr₄). All the samples have relatively large Stokes shifts, i.e. >260 nm. The shifts of the emission peaks might be attributed to the transient elastic lattice distortions of octahedra which were affected by the different organic cations.37 The 2D (RNH3)2SnBr4 perovskites were further studied using three-dimensional excitation-emission matrix (EEM) fluorescence spectroscopy (Fig. 2c). With the change of the excitation wavelength, the emission peaks showed a little shift, indicating that there were no other impurities or additional energy levels in our samples. Fig. 2d illustrates that, with increasing alkyl chain length, the PL QY is enhanced from 35% ($(C_6H_{13}NH_3)_2SnBr_4$) to 82% ($(C_8H_{17}NH_3)_2SnBr_4$) initially, but then experienced further reduction to 60.2% $((C_{12}H_{25}NH_3)_2SnBr_4)$ and 50.5% $((C_{18}H_{35}NH_3)_2SnBr_4)$. The PL QY versus excitation wavelength curves of 2D (C₆H₁₃NH₃)₂ $SnBr_4$ (a), $(C_8H_{17}NH_3)_2SnBr_4$ (b), $(C_{12}H_{25}NH_3)_2SnBr_4$ (c), and (C₁₈H₃₅NH₃)₂SnBr₄ (d) perovskites were also investigated (Fig. S7, ESI†). All these samples showed excitation dependent PL QY, achieving their highest values at 340 nm $((C_6H_{13}NH_3)_2SnBr_4, (C_8H_{17}NH_3)_2SnBr_4))$ and 320 nm $((C_{12}H_{25}NH_3)_2SnBr_4, (C_{18}H_{35}NH_3)_2SnBr_4)).$

Table 1 Summary of the optical properties of (RNH₃)₂SnBr₄ perovskites

Samples	Absorption peak (nm)	PL peak (nm)	FWHM (nm)	Stokes shift (meV)	Absolute PL QY (%)	$E_{\rm g}$ (eV)	$\tau_{ave} \; (\mu s)$
(C ₆ H ₁₃ NH ₃) ₂ SnBr ₄ (C ₈ H ₁₇ NH ₃) ₂ SnBr ₄ (C ₁₂ H ₂₅ NH ₃) ₂ SnBr ₄	335 344 338	618 610 603	136 137 134	283 266 265	35.0 82.0 60.2	3.48 3.38 3.20	1.60 4.99 5.31
$(C_{18}H_{35}NH_3)_2SnBr_4$	349	623	138	274	51.5	3.36	5.21

The time-resolved PL decay curves of 2D (RNH₃)₂SnBr₄ perovskites in Fig. 2e could be fitted by a single exponential function with a long lifetime of 1.60-5.31 µs. To illustrate the internal mechanism between the average PL lifetime and PLQY in various samples, we calculated the radiative $(k_r = PLQY/\tau_{avg})$ and nonradiative $(k_{\rm nr} = (1/\tau_{\rm avg}) - k_{\rm r})$ decay rates based on the PLQY and τ_{avg} . As shown in Table S1 (ESI†), with increasing $k_{\rm r}/k_{\rm nr}$, the nonradiative pathways were suppressed, and thus the PLQY of (RNH₃)₂SnBr₄ increased. ^{28,38-40} Table S1 (ESI†) shows that $(C_6H_{13}NH_3)_2SnBr_4$ has the lowest k_r/k_{nr} value of 0.5385. Therefore, we assumed that there were some non-ignorable non-radiative carrier trapping processes, which led to its lowest PLQY. 28,41-43 The differences in PLQY and lifetime among these (RNH₃)₂SnBr₄ indicated that the optical properties were influenced by the distortion of the structure.

In order to investigate the mechanism of broadband emission in our two-dimensional (2D) layered tin halide perovskites, we conducted a comprehensive review of 2D perovskites which also showed broadband emission, large Stokes shifts, and long lifetimes. 28,44-47 Li et al. reported the fabrication of 2D (RNH₃)₂SnBr₄ perovskites and their density functional theory (DFT) study revealed that these properties originated from a strong phonon coupling in the deformable lattice.²⁸ Multi-layered lead iodide perovskites were investigated via temperature-dependent photoluminescence (PL) spectroscopy and transient absorption (TA) spectroscopy. The results proved that the broad emission was related to the electronphonon coupling and structural deformation of the groundstate lattice arising from STEs. 47 The optical properties obtained in this study were consistent with the literature; therefore, we inferred that the observed broad emission, large Stokes shift, and long lifetimes of our samples stemmed from STEs. As shown in Fig. 2f, when excitons are trapped, the distortion of STEs compared to the ground state broadens the emission. The highly distorted octahedron generates more STEs, resulting in longer PL lifetimes. Fig. S8 (ESI†) shows the stability curves of 2D (RNH₃)₂SnBr₄ perovskites stored under ambient conditions for 30 days. All these samples exhibited good air stability. In particular, the PL QY of (C₁₈H₃₅NH₃)₂SnBr₄ perovskites decreased less than 1% after 30 days. It was obvious that longer alkylammonium chains could protect the [SnBr₆] octahedral luminescence centre more effectively, which in turn enhanced the stability of the 2D (RNH₃)₂SnBr₄ perovskites.²⁹

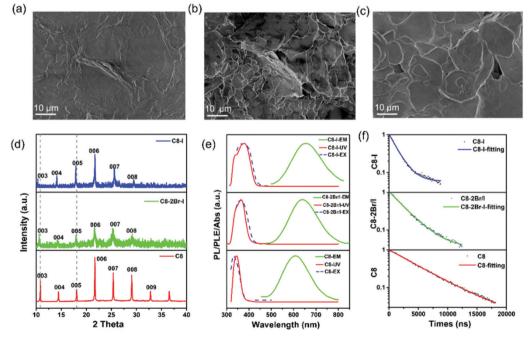


Fig. 3 Scanning electron microscopy (SEM) images of C8 (a), C8-2Br/I (b), and C8-I (c) perovskites. (d) Powder X-ray diffraction (PXRD) patterns of $(C_RH_{17}NH_{\tau})$ - SNX_4 perovskites (X = Br, 2Br/I, I). (e) UV-vis absorption, PL emission, and PL excitation spectra of the as-prepared samples. (f) Time-resolved PL decay spectra of $(C_8H_{17}NH_3)_2SnX_4$ perovskites (for simplicity, we use C8, C8-2Br/I and C8-I to represent $(C_8H_{17}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2Sn(2Br/I)_4$ and (C₈H₁₇NH₃)₂SnI₄ perovskites, respectively)

Materials Advances

Table 2 Summary of the optical properties of (RNH₃)₂SnX₄ perovskites

Samples	Absorption peak (nm)	PL peak position (nm)	Absolute PL QY (%)	Stokes shift (nm)	τ _{ave} (μs)
(C ₈ H ₁₇ NH ₃) ₂ SnBr ₄	332	610	82.0	278	4.99
(C ₈ H ₁₇ NH ₃) ₂ Sn(2Br/I) ₄	363	638	69.2	275	2.60
(C ₈ H ₁₇ NH ₃) ₂ SnI ₄	370	655	33.0	285	1.41

Similar to other halide perovskites, their halide portion of 2D (RNH₃)₂SnBr₄ perovskites can also be varied to tune the emission positions. 48 Various compositions of (C₈H₁₇NH₃)₂SnX₄ perovskites were synthesized by simply tuning the dosage of HBr and HI proportions. SEM images (Fig. 3a-c and Fig. S9, ESI†) showed that all the products possessed a 2D layered morphology. XRD patterns (Fig. 3d) of (C₈H₁₇NH₃)₂Sn(2Br/I)₄ and (C₈H₁₇NH₃)₂SnI₄ perovskites also implied periodic diffraction, which was an indication of a 2D layered structure and thus in agreement with the SEM results. In addition, we found that (003) planes showed a slight shift to lower angles from (C₈H₁₇NH₃)₂SnBr₄ to (C₈H₁₇NH₃)₂SnI₄ perovskites due to tin-halide bond expansion.²⁷ The FTIR spectra of 2D (RNH₃)₂SnX₄ perovskites are shown in Fig. S10 (ESI†), and it was pertinent to note that increasing I anion did not affect the position and intensity of the functional groups. Similar to lead halide perovskites, when the bromide ion was gradually replaced by the I- anion, the PLE peak red-shifted from 332 to 370 nm and the PL peak red-shifted from 610 to 655 nm, accompanied by the luminescence change from yellow to red (Fig. 3e). 48 The UV-vis absorption spectra of 2D (RNH₃)₂SnX₄ perovskites showed that the absorption peak red-shifted from 344 nm to 370 nm as the I/Br ratio increased. The band gap values were estimated to be 3.38 eV ((C₈H₁₇NH₃)₂SnBr₄), 2.89 eV $((C_8H_{17}NH_3)_2Sn(2Br/I)_4)$ and 3.17 eV $((C_8H_{17}NH_3)_2SnI_4)_7$ respectively (Fig. S11, ESI†). Time-resolved PL decay spectra of

(RNH₃)₂SnX₄ perovskites are shown in Fig. 3f. All the spectra were fitted with the single exponential decay function and the average PL lifetimes were as follows: 5 µs ((C₈H₁₇NH₃)₂SnBr₄), 2.6 μs ((C₈H₁₇NH₃)₂Sn(2Br/I)₄), and 1.41 μs ((C₈H₁₇NH₃)₂SnI₄), which further verified their self-trapping emission mechanism. As expected, the PL QYs of these products were (C₈H₁₇NH₃)₂SnBr₄ (82%), $(C_8H_{17}NH_3)_2Sn(2Br/I)_4$ (69.2%), and $(C_8H_{17}NH_3)_2SnI_4$ (33%), respectively, following the trend of the PL decay lifetime. The optical parameters of (RNH₃)₂SnX₄ are summarized in

Zn²⁺ doping has been considered as an effective method to achieve highly efficient perovskites. 49-51 Here, we introduced Zn^{2+} ions into 2D (RNH₃)₂SnX₄ (X = Br, I) perovskites for the first time. Fig. 4a and d show the UV-vis absorption, PL excitation, and PL emission spectra of Zn²⁺-doped $(C_8H_{17}NH_3)_2SnBr_4$ and Zn^{2+} -doped $(C_8H_{17}NH_3)_2SnI_4$ perovskites. After doping, the PL peaks of (C₈H₁₇NH₃)₂SnBr₄ and (C₈H₁₇NH₃)₂SnI₄ obviously shifted from 610 nm to 580 nm and from 655 nm to 630 nm, respectively. The blue-shift of PL peaks might result from lattice contraction.⁵² The XRD patterns of Zn²⁺-doped (RNH₃)₂SnX₄ (Fig. S12, ESI†) showed that, after doping, no new diffraction peaks appeared. In addition, the diffraction peaks slightly shifted to higher angles, indicating that the doping of zinc did not change the crystallinity of the perovskites but only contracted the lattice.⁵³ We included the PL decay of both the undoped sample and doped samples for comparison as shown in Fig. 4b and e. The Zn2+-doped $(C_8H_{17}NH_3)_2SnBr_4$ and Zn^{2+} -doped $(C_8H_{17}NH_3)_2SnI_4$ perovskites could also be fitted by a single exponential function with a long lifetime of 4.4 µs and 1.9 µs, respectively. The corresponding τ_{avg} and R^2 values are listed in Table S2 (ESI†); compared with undoped samples, the lifetime of doped samples did not show any obvious change. Interestingly, both

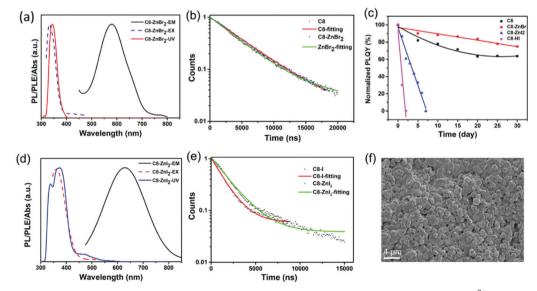


Fig. 4 (a and d) UV-vis absorption, PL emission, and PL excitation spectra of the as-prepared C8 and C8-I doped with Zn^{2+} . (b and e) Time-resolved PL decay and fitting curves. (c) Stability curves displayed by the PL QY of undoped and Zn²⁺-doped samples. (f) Scanning electron microscopy (SEM) images of Zn^{2+} -doped C8-I samples (for simplicity, we use C8, C8-HI, C8-ZnBr₂ and C8-ZnI₂ to represent $(C_8H_{17}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2SnBr_4$ (C₈H₁₇NH₃)₂SnBr₄ and Zn²⁺-doped (C₈H₁₇NH₃)₂SnI₄ perovskites, respectively)

Paper Materials Advances

Zn²⁺-doped (C₈H₁₇NH₃)₂SnBr₄ (82% to 85%) and (C₈H₁₇NH₃)₂SnI₄ (33% to 50%) perovskites exhibited higher PL QYs compared with undoped ones, which might have resulted from fewer defects and suppressed nonradiative pathways in the doped perovskites. $^{50,54-56}$ We calculated the radiative ($k_r = PLQY/\tau_{avg}$) and nonradiative $(k_{\rm nr} = (1/\tau_{\rm avg}) - k_{\rm r})$ decay rates of undoped and doped samples based on the PLQY and τ_{avg} . The results are summarized in Table S3 (ESI†), and prove that, after zincdoping, the nonradiative pathways were inhibited. 38-40 Furthermore, the alloying significantly improved the stability of (C₈H₁₇NH₃)₂SnBr₄ and (C₈H₁₇NH₃)₂SnI₄ perovskites *via* lattice contraction (Fig. 4c).⁵² The SEM images (Fig. 4f) showed that Zn²⁺-doped (C₈H₁₇NH₃)₂SnI₄ perovskites possessed uniform round sheet morphology with an average size of 690 nm. The real elemental composition of Zn²⁺/Sn²⁺ of Zn²⁺-doped (C₈H₁₇NH₃)₂SnBr₄ and (C₈H₁₇NH₃)₂SnI₄ perovskites were 3% and 4%, respectively, confirmed by inductively coupled plasma optical emission spectrometry (ICPOES).

The $\rm Zn^{2+}$ -doped ($\rm C_8H_{17}NH_3$) $_2\rm SnBr_4$ perovskite was adopted as a yellow phosphor for UV pumped LED fabrication (Fig. 5). Both $\rm Zn^{2+}$ -doped ($\rm C_8H_{17}NH_3$) $_2\rm SnBr_4$ in the PS film (Fig. 5a) and the $\rm Zn^{2+}$ -doped ($\rm C_8H_{17}NH_3$) $_2\rm SnBr_4$ LED device (Fig. 5b) showed bright yellow emission. As shown in Fig. 5d, the CIE coordinates, colour rendering index (CRI) and correlated color temperature (CCT) of the LED were measured to be (0.5060, 0.4542), 75 and 2455 K, respectively. In order to test the stability of the yellow LED, we recorded a series of PL spectral curves by tuning the driving voltage (Fig. 5c). It is worth noting that the PL intensity increased with driving voltage changing from 3 V to 9 V, without an obvious PL peak shift, indicating its good colour

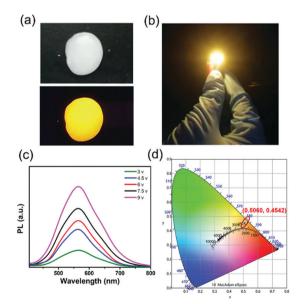


Fig. 5 (a) Images of Zn^{2+} -doped ($C_8H_{17}NH_3$) $_2SnBr_4$ yellow phosphorembedded in the PS film under sunlight (top) and 365 nm UV light (bottom). (b) 365 nm UV light pumped yellow LED device. (c) PL spectra of a yellow LED obtained by varying the driving voltage. (d) Chromaticity coordinates of Zn^{2+} -doped ($C_8H_{17}NH_3$) $_2SnBr_4$ yellow phosphor plotted on the CIE1931 chromaticity chart.

stability. These results motivated us to explore further applications including in display backlights.

Conclusions

In summary, we have demonstrated the synthesis of the leadfree $(C_6H_{13}NH_3)_2SnBr_4$, $(C_8H_{17}NH_3)_2SnBr_4$, $(C_{12}H_{25}NH_3)_2SnBr_4$ and (C₁₈H₃₅NH₃)₂SnBr₄ 2D perovskites with bright PL emission properties through a facile hot-injection method using the low-cost and environment-friendly hydrobromic acid and stannous 2-ethylhexanoate as the precursors. Among them, (C₈H₁₇NH₃)₂SnBr₄ perovskites with broad and bright yellow emission centered at 610 nm achieved the highest PL QY (82%). Interestingly, we found that the length of organic amine cations could strongly affect the emission peak, which might be attributed to the transient elastic lattice distortions. Through the incorporation of Zn2+ ions, the 2D (C8H17NH3)2SnBr4 showed an enhanced stability and improved morphology uniformity. A yellow-emitting LED was fabricated using the Zn²⁺doped (C₈H₁₇NH₃)₂SnBr₄ perovskite. These 2D perovskites are promising phosphors with potential applications in future solid-state lighting and display technologies.

Experiments

Chemicals

1-Octadecene (ODE, Aladdin, GC > 90%), oleic acid (OA, Aladdin, AR, 85%), hexylamine (Aladdin, AR, 99%), n-octylamine (Aladdin, AR, 99%), dodecylamine (Aladdin, AR, 98%), oleylamine (Aladdin, AR, 80–90%), hydrobromic acid (HBr, Macklin, AR, 48 wt% in H_2O), hydroiodic acid (HI, Aladdin, AR, 55.0–58.0% with \leq 1.5% H_3PO_2), zinc bromide (Macklin, AR), zinc iodide (Aladdin, AR, \geq 98%), stannous 2-ethylhexanoate (Aladdin, AR, 95%), n-hexane (Macklin, AR, 97%), and polystyrene (PS, Aladdin) were purchased and used without further purification.

Synthesis of (C₈H₁₇NH₃)₂SnX₄

To prepare the stannous 2-ethylhexanoate/ODE solution, 370 μL stannous 2-ethylhexanoate was added into 740 μL ODE, and the solution was mixed well under ultrasonication. In a typical synthesis, ODE (20 mL), OA (0.4 mL), n-octylamine (0.4 mL) and HBr (163 µL) were added to a 50 mL three-neck round bottom flask and degassed at 120 °C for 2 h. The temperature was increased to 180 °C under a N2 atmosphere. Then 780 µL of the stannous 2-ethylhexanoate/ODE solution was swiftly injected, and the flask was immersed in an ice bath to stop the reaction after 10 s. The crude solution was dispersed in hexane and centrifuged at 10 000 rpm for 2 min, and the supernatant was discarded. Finally, a white precipitate of 2D the (C₈H₁₇NH₃)₂SnBr₄ perovskite was obtained with strong yellow fluorescence under UV light. For the synthesis of $(C_8H_{17}NH_3)_2Sn(2Br/I)_4$ or $(C_8H_{17}NH_3)_2SnI_4$, the variable compositions were achieved by controlling the ratio of HBr/HI.

Materials Advances Paper

Synthesis of (RNH₃)₂SnBr₄

To synthesize other (RNH₃)₂SnBr₄ perovskites, octylamine was replaced by another organic amine chain with the same molar ratio.

Synthesis of Zn²⁺-doped (C₈H₁₇NH₃)₂SnX₄

To prepare $Zn^{2^+}\text{-doped }(C_8H_{17}NH_3)_2SnX_4\text{, }10\%\ ZnBr_2\ or\ ZnI_2$ (by the molar ratio of Sn) was added into a mixed solution of ODE (20 mL), OA (0.4 mL), n-octylamine (0.4 mL) and HBr (163 μL). The subsequent steps were the same as in the synthesis of $(C_8H_{17}NH_3)_2SnBr_4$.

Fabrication of LEDs

Yellow Zn²⁺-doped (C₈H₁₇NH₃)₂SnBr₄ phosphor was well mixed with 25% polystyrene (PS)-dichloromethane solution. The mixed phosphor of PS paste was dried on a 365 nm ultraviolet LED chip (1 W, 365 nm) in air to fabricate a yellow LED lamp.

Characterization

Powder X-ray diffraction (PXRD) was carried out using a Bruker AXS D8 X-ray diffractometer (USA) equipped with monochromated Cu K α radiation (λ = 1.5418 Å). The diffraction patterns were scanned in the 2θ range of 10–40 degrees with a step size of 0.06 at room temperature. X-Ray photoelectron spectroscopy (XPS) was performed using an achromatic Al Kα source (1486.6 eV) and a double pass cylindrical mirror analyzer (ULVAC-PHI 5000 VersaProbe) (Japan). Fourier transform infrared (FTIR) spectroscopy was conducted using a Fourier transform infrared spectrometer (Nicolet NEXUS 870) (USA). The UV-vis absorption spectra were measured using a Shimadzu UV-3600 Plus spectrophotometer (Japan) under ambient conditions. Photoluminescence (PL) measurements were conducted using a Horiba PTI QuantaMaster 400 steady-state fluorescence system (Japan) under ambient conditions. Scanning electron microscopy (SEM) was performed on a Zeiss ULTRA55 electron microscope. The absolute fluorescence quantum yields (PLQYs) were measured using a Horiba PTI QuantaMaster 400 steady-state fluorescence system with an integrated sphere and doublechecked with a Hamamatsu Photonics Quantaurus-QY (model: C11347-11) under ambient conditions. Transmission electron microscopy (TEM) was carried out on an FEI TECNAI G2 F20 and an electron microscope operating at 200 kV. The available spectral resolution is about 0.1 nm. Time-resolved PL emission decay curves were collected at room temperature and detected using a low temperature time-resolved fluorescence system (Edinburgh, FLS920) (UK) with the samples being prepared by depositing different perovskites on glass substrates directly. Elemental concentrations of Zn²⁺/Sn²⁺ were analyzed *via* inductively coupled plasma optical emission spectrometry (ICP-OES) using a Skyray[®] ICP-3000 instrument.

Author contributions

Y. L. synthesized the samples, conducted the measurements, and wrote the first draft of the manuscript. A. W. helped with

the measurement of the samples and co-drafted the manuscript. J. W., C. W., W. M. and Z. L. revised the manuscript. G. H and S. S. helped with the measurement of the PL decay. J. S. and W. L. helped with the ICP measurements. Z. D. supervised the project. All authors analysed the data and contributed to the discussion.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the Natural Science Foundation of China (22075129) and the Natural Science Foundation of Jiangsu Province (Grant No. BK20180339 and BZ2018008).

Notes and references

- 1 Z. Tan, R. S. Moghaddam, M. L. Lai, P. Docampo, R. Higler, F. Deschler, M. Price, A. Sadhanala, L. M. Pazos, D. Credgington, F. Hanusch, T. Bein, H. J. Snaith and R. H. Friend, Nat. Nanotechnol., 2014, 9, 687-692.
- 2 M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, Science, 2012, 338, 643-647.
- 3 N. J. Jeon, J. H. Noh, W. S. Yang, Y. C. Kim, S. Ryu, J. Seo and S. I. Seok, Nature, 2015, 517, 476-480.
- 4 M. V. Kovalenko, L. Protesescu and M. I. Bodnarchuk, Science, 2017, 358, 745-750.
- 5 H. Huang, A. S. Susha, S. V. Kershaw, T. F. Hung and A. L. Rogach, Adv. Sci., 2015, 2, 1500194.
- 6 L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh and M. V. Kovalenko, Nano Lett., 2015, 15, 3692-3696.
- 7 W. Liu, Q. Lin, H. Li, K. Wu, I. Robel, J. M. Pietryga and V. I. Klimov, J. Am. Chem. Soc., 2016, 138, 14954-14961.
- 8 X. Yuan, S. Ji, M. C. De Siena, L. Fei, Z. Zhao, Y. Wang, H. Li, J. Zhao and D. R. Gamelin, Chem. Mater., 2017, 29, 8003-8011.
- 9 K. P. Marshall, R. I. Walton and R. A. Hatton, J. Mater. Chem. A, 2015, 3, 11631-11640.
- 10 C. Huo, B. Cai, Z. Yuan, B. Ma and H. Zeng, Small Methods, 2017, 1, 1600018.
- 11 T. C. Jellicoe, J. M. Richter, H. F. J. Glass, M. Tabachnyk, R. Brady, S. E. Dutton, A. Rao, R. H. Friend, D. Credgington, N. C. Greenham and M. L. Böhm, J. Am. Chem. Soc., 2016, 138, 2941-2944.
- 12 B. Yang, F. Hong, J. Chen, Y. Tang, L. Yang, Y. Sang, X. Xia, J. Guo, H. He, S. Yang, W. Deng and K. Han, Angew. Chem., Int. Ed., 2019, 58, 2278-2283.
- 13 B. Yang, X. Mao, F. Hong, W. Meng, Y. Tang, X. Xia, S. Yang, W. Deng and K. Han, J. Am. Chem. Soc., 2018, 140, 17001-17006.
- 14 S. Liu, B. Yang, J. Chen, D. Wei, D. Zheng, Q. Kong, W. Deng and K. Han, Angew. Chem., Int. Ed., 2020, 59, 21925-21929.
- 15 W. Yang, F. Igbari, Y. Lou, Z. Wang and L. Liao, Adv. Energy Mater., 2020, 10, 1902584.

Paper

16 G. Xing, M. H. Kumar, W. K. Chong, X. Liu, Y. Cai, H. Ding, M. Asta, M. Grätzel, S. Mhaisalkar, N. Mathews and T. C. Sum, Adv. Mater., 2016, 28, 8191–8196.

- 17 H. Fang, S. Adjokatse, S. Shao, J. Even and M. A. Loi, *Nat. Commun.*, 2018, **9**, 243.
- 18 F. Wang, J. Ma, F. Xie, L. Li, J. Chen, J. Fan and N. Zhao, *Adv. Funct. Mater.*, 2016, **26**, 3417–3423.
- 19 H. Liang, F. Yuan, A. Johnston, C. Gao, H. Choubisa, Y. Gao, Y. Wang, L. K. Sagar, B. Sun, P. Li, G. Bappi, B. Chen, J. Li, Y. Wang, Y. Dong, D. Ma, Y. Gao, Y. Liu, M. Yuan, M. I. Saidaminov, S. Hoogland, Z.-H. Lu and E. H. Sargent, Adv. Sci., 2020, 7, 1903213.
- 20 C. Gao, Y. Jiang, C. Sun, J. Han, T. He, Y. Huang, K. Yao, M. Han, X. Wang, Y. Wang, Y. Gao, Y. Liu, M. Yuan and H. Liang, ACS Photonics, 2020, 7, 1915–1922.
- 21 A. Wang, X. Yan, M. Zhang, S. Sun, M. Yang, W. Shen, P. Wang and Z. Deng, *Chem. Mater.*, 2016, 28, 8132–8140.
- 22 Z. Tan, J. Li, C. Zhang, Z. Li, Q. Hu, Z. Xiao, T. Kamiya, H. Hosono, G. Niu, E. Lifshitz, Y. Cheng and J. Tang, *Adv. Funct. Mater.*, 2018, 28, 1801131.
- 23 M. I. Saidaminov, O. F. Mohammed and O. M. Bakr, *ACS Energy Lett.*, 2017, 2, 889–896.
- 24 L. Lanzetta, J. M. Marin-Beloqui, I. Sanchez-Molina, D. Ding and S. A. Haque, *ACS Energy Lett.*, 2017, 2, 1662–1668.
- 25 P. Fu, M. Huang, Y. Shang, N. Yu, H. Zhou, Y. Zhang, S. Chen, J. Gong and Z. Ning, ACS Appl. Mater. Interfaces, 2018, 10, 34363–34369.
- 26 X. Zhang, C. Wang, Y. Zhang, X. Zhang, S. Wang, M. Lu, H. Cui, S. V. Kershaw, W. W. Yu and A. L. Rogach, *ACS Energy Lett.*, 2019, 4, 242–248.
- 27 A. Wang, Y. Guo, Z. Zhou, X. Niu, Y. Wang, F. Muhammad, H. Li, T. Zhang, J. Wang, S. Nie and Z. Deng, *Chem. Sci.*, 2019, 10, 4573–4579.
- 28 L. Hou, Y. Zhu, J. Zhu and C. Li, *J. Phys. Chem. C*, 2019, 123, 31279–31285.
- 29 F. M. Li, Y. Xie, Y. Hu, M. Long, Y. Zhang, J. B. Xu, M. Qin, X. Lu and M. Liu, ACS Energy Lett., 2020, 5, 1422–1429.
- 30 A. Dutta, S. K. Dutta, S. Das Adhikari and N. Pradhan, *Angew. Chem., Int. Ed.*, 2018, **57**, 9083–9087.
- 31 C. C. Stoumpos, D. H. Cao, D. J. Clark, J. Young, J. M. Rondinelli, J. I. Jang, J. T. Hupp and M. G. Kanatzidis, *Chem. Mater.*, 2016, 28, 2852–2867.
- 32 D. H. Cao, C. C. Stoumpos, O. K. Farha, J. T. Hupp and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2015, 137, 7843–7850.
- 33 S. Mourdikoudis and L. Liz-Marzán, Chem. Mater., 2013, 25, 1465–1476.
- 34 W. Xu and T. Wang, Langmuir, 2017, 33, 82-90.
- 35 Y. Dang, Y. Zhou, X. Liu, D. Ju, S. Xia, H. Xia and X. Tao, *Angew. Chem., Int. Ed.*, 2016, 55, 3447–3450.
- 36 H. Lin, C. Zhou, Y. Tian, T. Siegrist and B. Ma, ACS Energy Lett., 2018, 3, 54–62.

- 37 C. Quarti, N. Marchal and D. Beljonne, *J. Phys. Chem. Lett.*, 2018, **9**, 3416–3424.
- 38 B. Yang, J. Chen, F. Hong, X. Mao, K. Zheng, S. Yang, Y. Li, T. Pullerits, W. Deng and K. Han, *Angew. Chem., Int. Ed.*, 2017, 56, 12471–12475.
- 39 B. Yang and K. Han, Acc. Chem. Res., 2019, 52, 3188-3198.
- 40 B. Yang, J. Chen, S. Yang, F. Hong, L. Sun, P. Han, T. Pullerits, W. Deng and K. Han, *Angew. Chem., Int. Ed.*, 2018, 130, 5457–5461.
- 41 J. Tong, J. Wu, W. Shen, Y. Zhang, Y. Liu, T. Zhang, S. Nie, Z. Deng, J. Tong, J. Wu, W. Shen, Y. Zhang, Y. Liu, T. Zhang, S. Nie and Z. Deng, ACS Appl. Mater. Interfaces, 2019, 11, 9317–9325.
- 42 G. Li, J. Huang, H. Zhu, Y. Li, J. Tang and Y. Jiang, *Chem. Mater.*, 2018, **30**, 6099–6107.
- 43 Z. Liu, Y. Zhang, Y. Fan, Z. Chen, Z. Tang, J. Zhao, Y. Lv, J. Lin, X. Guo, J. Zhang and X. Liu, ACS Appl. Mater. Interfaces, 2018, 10, 13053-13061.
- 44 M. D. Smith and H. I. Karunadasa, *Acc. Chem. Res.*, 2018, **51**, 619–627.
- 45 L. Mao, Y. Wu, C. C. Stoumpos, B. Traore, C. Katan, J. Even, M. R. Wasielewski and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2017, 139, 11956–11963.
- 46 K. Thirumal, W. K. Chong, W. Xie, R. Ganguly, S. K. Muduli, M. Sherburne, M. Asta, S. Mhaisalkar, T. C. Sum, H. S. Soo and N. Mathews, *Chem. Mater.*, 2017, 29, 3947–3953.
- 47 W. Paritmongkol, E. R. Powers, N. S. Dahod and W. A. Tisdale, *J. Phys. Chem. Lett.*, 2020, **11**, 8565–8572.
- 48 G. Nedelcu, L. Protesescu, S. Yakunin, M. I. Bodnarchuk, M. J. Grotevent and M. V. Kovalenko, *Nano Lett.*, 2015, 15, 5635–5640.
- 49 M. Que, W. Chen, P. Chen, J. Liu, X. Yin, B. Gao and W. Que, *Chem. Phys.*, 2019, 517, 80–84.
- 50 J. Li, J. Chen, L. Xu, S. Liu, S. Lan, X. Li and J. Song, *Mater. Chem. Front.*, 2020, 4, 1444–1453.
- 51 R. Ren, Z. Wang, X. Meng, C. Xu, J. Qiao, W. Sun and K. Sun, ACS Appl. Mater. Interfaces, 2020, 12, 23959–23967.
- 52 X. Shen, Y. Zhang, S. V. Kershaw, T. Li, C. Wang, X. Zhang, W. Wang, D. Li, Y. Wang, M. Lu, L. Zhang, C. Sun, D. Zhao, G. Qin, X. Bai, W. W. Yu and A. L. Rogach, *Nano Lett.*, 2019, 19, 1552–1559.
- 53 G. Pan, X. Bai, D. Yang, X. Chen, P. Jing, S. Qu, L. Zhang, D. Zhou, J. Zhu, W. Xu, B. Dong and H. Song, *Nano Lett.*, 2017, 17, 8005–8011.
- 54 F. Li, Y. Liu, H. Wang, Q. Zhan, Q. Liu and Z. Xia, *Chem. Mater.*, 2018, 30, 8546–8554.
- 55 W. Zhao, D. Yang, Z. Yang and S. Liu, *Mater. Today Energy*, 2017, 5, 205–213.
- 56 W. van der Stam, J. J. Geuchies, T. Altantzis, K. H. W. van den Bos, J. D. Meeldijk, S. Van Aert, S. Bals, D. Vanmaekelbergh and C. de Mello Donega, *J. Am. Chem. Soc.*, 2017, **139**, 4087–4097.