

Cite this: *RSC Adv.*, 2017, 7, 10718

Synthesis and characterization of metallo-supramolecular polymers from thiophene-based unimers bearing pybox ligands†

Sviatoslav Hladysh,^{*a} Daniela Václavková,^b David Vrbata,^a Dmitriy Bondarev,^{bc} David Havlíček,^d Jan Svoboda,^e Jiří Zedník^a and Jiří Vohlídal^a

A series of novel metallo-supramolecular polymers was successfully prepared, based on 2,6-bis(2-oxazoliny)pyridine building blocks consisting of pyridine flanked by two oxazoline rings as a tridentate binding site bridged with thiophene, bithiophene and thienothiophene as a linker, beginning from a cheap and commercially available 1,4-dihydro-4-oxo-2,6-pyridinedicarboxylic (chelidamic) acid. Metallo-supramolecular polymers were obtained and spectroscopically characterized upon treatment of the synthesized building blocks, also known as unimers, with the following metal ions: Fe²⁺, Zn²⁺, Ni²⁺, Cu²⁺. During the self-assembly process of the prepared unimers with a Cu²⁺ ion coupler, UV/vis investigation showed the highest shift of absorption maxima to lower energies, contrary to the Fe²⁺ ion couplers where the lowest value of shift was detected, compared to the free unimer. Upon the complexation of the Fe²⁺ ion coupler with selected unimers, the appearance was observed of new absorption bands around 600 nm ascribable to metal-to-ligand charge-transfer transitions. The luminescence study of the complexation of the synthesized unimers with Zn²⁺ exhibited a high fluorescence increase with an increase of metal ion concentration. Adversely, all of the other metals only showed fluorescence quenching.

Received 11th November 2016
Accepted 27th January 2017

DOI: 10.1039/c6ra26665g

rsc.li/rsc-advances

Introduction

Supramolecular materials have attracted the attention of many researches during the past decades.^{1,2} An important subclass of these materials is represented by metallo-supramolecular polymers (MSPs).³ They are typically built from low-molar-mass (multidentate) organic molecules (denoted as unimers (U) – analogous to the monomer unit in the classic polymer or micelle building units) that are self-assembled into larger arrays or chains by non-covalent (labile) interactions typical of coordination bonds with metal ion couplers (ICs). This lability of the coordination bonds gives the resulting materials a dynamic nature and, consequently, these materials belong to the family of materials called dynamers (a term introduced by Nobel Prize

laureate Jean-Marie Lehn).⁴ Labile bonding introduces interesting new properties and allows the possibility of precise system tailoring by the structure of unimers and character and concentration of ion couplers.^{5–8} The self-assembly process is achieved by introducing the ion coupler into the unimer solution, or *vice versa*. This process proceeds by the formation of coordination bonds (complexation) between the Us and ICs, leading to the formation of MSPs by the self-assembly process. The term complexation is also used for the formation of “model” complexes that are also presented in this contribution. Therefore, complexation is a general tool for the preparation of either MSPs by the self-assembly process or simple metal–ligand complexes prepared by coordination with standard ligand possessing only one chelating binding site. Large self-assemblies are formed in the case of multifunctional Us possessing at least two chelating binding sites. Most MSPs are typically processed in the solid state as thin films. There are two aspects of MSP stability in solution. The first is represented by the thermodynamic stability constant of the coordination sites of the U molecules and selected metal ICs. The second aspect is related to the kinetics of the labile coordination bonding, characterized by the exchange rate of the free unimer and in the supramolecular assembly. The kinetic aspect of equilibrium in solution is denoted as a constitutional dynamic in further text.^{9,10}

The application potential of MSPs is broad across various fields: MSPs with low T_g are utilized in self-healing applications^{11,12} as well as various responsive systems,^{13–16} including

^aDepartment of Physical and Macromolecular Chemistry, Faculty of Science, Charles University in Prague, Hlavova 8, CZ-12840 Prague 2, Czech Republic. E-mail: sviatoslavhladysh@gmail.com


^bTomas Bata University in Zlin, Faculty of Technology, Department of Polymer Engineering, Vavrečkova 275, CZ-762 72 Zlin, Czech Republic

^cPolymer Institute, Slovak Academy of Sciences, Dubravska cesta 9, 845 41 Bratislava, Slovakia

^dDepartment of Inorganic Chemistry, Faculty of Science, Charles University in Prague, Hlavova 8, CZ-12840 Prague 2, Czech Republic

^eInstitute of Macromolecular Chemistry AS CR, v.v.i., Heyrovsky Sq. 2, 16206, Prague 6, Czech Republic

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra26665g

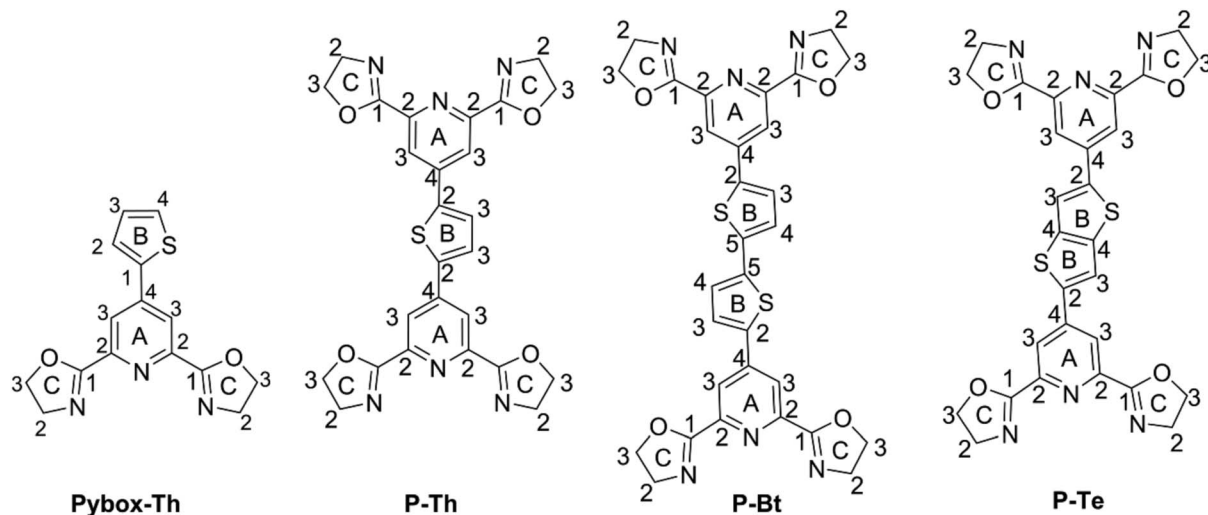

Scheme 1 Synthesized unimers (U) and ligands with formal group numbering for NMR.

absorption and emission bands showed a tendency to increase with the increase of band gap energy.

Self-assembly of unimers to MSPs in solution. A UV/vis spectroscopy study of the prepared unimers upon their complexation into MSPs, using the various metal ion couplers Fe^{2+} , Zn^{2+} , Ni^{2+} and Cu^{2+} was performed. A mixed solvent of chloroform/methanol (1/1 by volume) was used to dissolve the unimers and metal ions. This solvent system was found to be the most suitable for dissolving all the components during the MSP preparation. Moreover, this solvent mixture was chosen as the simplest representative of polar and non-polar solvents for forming a positive azeotrope. Standard dipolar aprotic solvents, such as pure dimethyl sulfoxide (DMSO) or *N,N*-dimethylformamide (DMF), were not used because of their inhibition of supramolecular system formation in the above-mentioned solvents at the concentration (2×10^{-4} M) used in the UV/vis study. But an increase of concentration in DMSO of two orders up to 2×10^{-2} M provides the formation of MSPs, as was also observed by an NMR titration study. Therefore, it is obvious that the thermodynamic solvent quality strongly influences the stability constants of species formed in the mixture.⁴⁷

A set of solutions of constant unimer's concentration (2×10^{-4} M) and metal ions (2×10^{-2} M) was prepared as the

chosen mixed solvent (chloroform/methanol) for the UV/vis titration study. By the method of a stepwise increase of the ion coupler to unimer ratio, MSPs systems were obtained that were subsequently studied spectroscopically. The $[\text{IC}]/[\text{U}]$ ratio is denoted as r in further text.

The results are summarized in Fig. 1 for **P-Bt**, and the rest of the titration results of **P-Th** and **P-Te** with various ICs are shown in Fig. S3 and S4 in the ESI.† The optical parameters of all the unimers and metallo-supramolecular polymers are shown in Table 1.

The self-assembly process of unimers with ICs is accompanied by the appearance of new absorption bands. A UV/vis study of this process allows us to track the formation of MSPs. The absorption spectra obtained for studied systems can be analyzed by the three stages of assembly using different values of r . The first stage covers ratios of r from 0 to 0.5 and shows: (i) the negligible changes of band shape, (ii) the appearance of new absorption bands and (iii) the formation of isosbestic points (IP) indicating the transformation of free U species into other defined forms in solution. The stoichiometry hints that the new species could be the dimer (U-(IC)-U), analogous to the above-mentioned "butterfly dimer".⁴⁶ The second stage of the assembly process, from r 0.6 to 1, shows the shift of newly

Table 1 Optical data of unimers (U) with different metal ions: λ_A wavelength of absorption maximum (nm); ϵ_{max} molar absorption coefficient in absorption maxima ($\text{dm}^3 \text{mol}^{-1} \text{cm}^{-1}$); λ_e absorption edge (nm); λ_F wavelength of emission maximum (nm); S Stokes shift (cm^{-1}), r unimer to metal ion ratio

IC	P-Th						P-Bt						P-Te					
	r	λ_A nm	λ_e nm	ϵ_{max}	λ_F nm	S cm^{-1}	λ_A nm	λ_e nm	ϵ_{max}	λ_F nm	S cm^{-1}	λ_A nm	λ_e nm	ϵ_{max}	λ_F nm	S cm^{-1}		
U	0	350	491	8.9	404	3820	400	526	12.6	532	6210	373	516	15.3	510	7209		
Fe^{2+}	1	371	698	7.2	408	2445	411	687	10.5	480	3490	398	702	10.9	440	2390		
Zn^{2+}	1	380	516	8.7	434	3270	445	625	13.3	542	4020	422	566	14.6	483	2990		
Ni^{2+}	1	375	523	10.6	409	2210	449	594	15.6	496	2110	427	567	17.9	465	1910		
Cu^{2+}	1	388	538	10.2	421	2020	457	632	12.8	501	1920	433	583	14.9	474	1990		



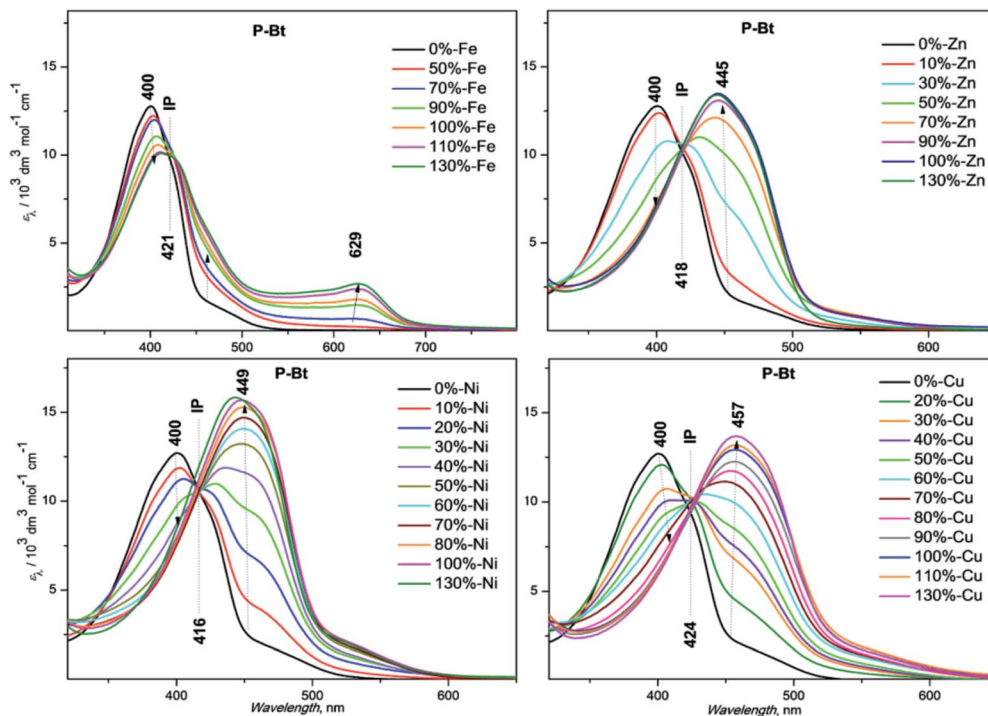


Fig. 1 UV/vis titration spectra of P-Bt (2×10^{-4} M, based on the monomer unit), with ion couplers (2×10^{-2} M).

formed absorption bands to lower energies accompanied with an increase in the molar absorption coefficient (ϵ) (except Fe^{2+} IC, which shows a decrease of ϵ). The last stage (where $r > 1$) does not show significant changes in the absorption spectra and can be considered as a depolymerization process of the MSPs, where the pybox end moiety is end-capped by IC coordinated only from one side. According to the UV/vis analysis of all stages of the self-assembly process, MSPs gain the maximum length at a ratio (r) of about 1. As already mentioned above, the studied system is dynamic and the described model serves as a rough description of the presumed behavior. It is obvious that the various chemical species present in the mixture depends upon the stability constants of each compound. Consequently, at $r = 0.5$ (as an example) “butterfly dimers” are present in the mixture as well as longer polymeric fragments, so free IC and U could be expected in the reaction mixture. It can be concluded that, at selected overall concentrations of the components in the system, the model fits well the observed spectral behavior during its titration course. In summary, the polymerization degree is not dependent only on the values of r , but is also a function of the overall concentration and solvents used.

Absorption maximal positions differ in their dependence on the metal ion coupler used for the MSP preparation. The highest shifts to longer wavelengths (about 50 nm) compared to the corresponding free U is observed in the case of Cu^{2+} (see ESI, Fig. S5†). Maximal absorption shifts to longer wavelengths were detected during the titration experiment (only 20 nm) for Fe^{2+} at $r = 1$. But this MSP displays new absorption bands at around 630 nm that are attributed to the metal-to-ligand charge transfer transition (MLCT) (see Fig. 1, S3 and S4 in the ESI†).

Additionally, the influence of r on the absorption maximal position of newly formed bands corresponding to MSP formation has been characterized by means of graphical dependence (see ESI,† Fig. S6†). In all the cases, we observed a similar trend, with significant shifts to lower energies after the addition of the first portion of IC ($r = 0.3$). The stepwise increase of IC concentration leads to further shifts of absorption band positions to lower energies. The maximal absorption edges of MSPs with various ICs at $r = 1$ are summarized in Table 1. The Ni^{2+} ion coupler showed the lowest energy maximum position at $r = 0.5$. Further addition of the Ni^{2+} IC has practically no influence on the absorption maximum position. This observation indicates that the thermodynamically preferred motif in the case of the Ni^{2+} IC is the “butterfly dimer” U-IC-U. Further addition of the Ni^{2+} IC probably leads to the prolongation of the MSP chains formed. The rest of the ICs, Fe^{2+} , Zn^{2+} , Cu^{2+} , exhibit a gradual shift of absorption bands to lower energies r (from 0.1 up to 1). In these cases, the IC-U moiety was formed in the first step (the ion coupler is coordinated only by one tridentate pybox moiety). The next step is represented by the dimer formation of a U-IC-U type, followed by MSP chain formation with increasing r . The longest MSP chains are expected at r equals unity in all the studied systems (see Table 1 above, a summary of all the basic optical properties). The further addition of IC ions probably leads to the shortening of MSP chains and to the formation of MSPs end-capped by an IC moiety on the chain-ends. All the systems are of a dynamic nature. It can be presumed that chemical relaxation (rate of reaching the equilibrium) is different in dependence on the U and IC character in each experiment. 1 day (24 h) was found to be sufficient for the



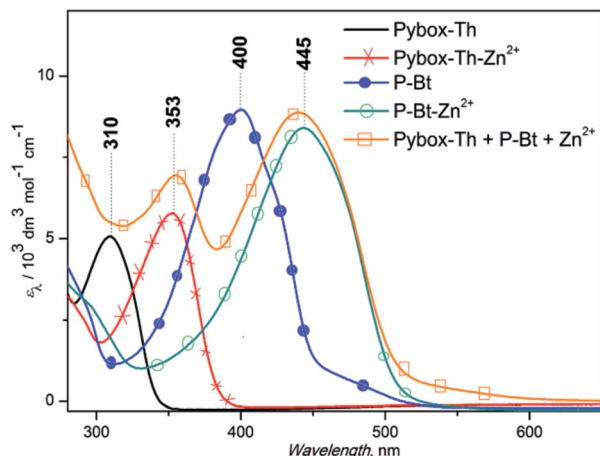


Fig. 2 Absorption spectra of P-Bt end-capping experiment.

equilibration of all the studied systems. It is presumed that 24 h is a sufficient time for chemical relaxation of all the studied systems and all the components are in an inner equilibrium. But it is worth mentioning that even after 24 h, supramolecular systems are still of a dynamic nature and the introduction of additional portions of IC or U leads to re-equilibration. This process is more precisely described below as an end-capping experiment.

The observed behavior indicates that a change in the overall concentrations of all the components in the studied system leads to immediate re-equilibration of the studied system in the solution. Unfortunately, this fact disallows a GPC/SEC study of the prepared MSPs. The injection of the studied mixture into GPC columns leads to several orders of dilution in the studied materials. Chemical relaxation (rate of reaching equilibrium) appears quickly enough to decompose the formed MSPs. Only free unimer is observed at the end of the GPC path in all cases. The ion coupler remains bound on the styragel-based GPC columns. Strong chelating reagents, like bipyridine or EDTA, must be used to release the metal ions from the column.

The end-capping experiment of the end-groups of MSP was performed based on **P-Bt** unimer and Zn^{2+} ion coupler ($r = 1$) by the addition of a **Pybox-Th** ligand. The addition of the **Pybox-Th** ligand to the solution of MSP leads to the appearance of a new absorption band with a maximum at 353 nm and a shoulder at 550 nm (yellow line, Fig. 2). The complexation study of the **Pybox-Th** ligand with the Zn^{2+} IC showed shifts to a lower energy with an absorption maximum at 353 nm. The fact that the Zn^{2+}

ICs at the chain-ends of the MSP are end-capped by **Pybox-Th** ligands confirms the dynamic character of the studied MSPs in solution.

Study of solid state unimers and corresponding MSPs. The absorption spectra of **P-Th**, **P-Bt**, **P-Te** and MSPs based on the above mentioned unimers with Zn^{2+} IC in solid thin films were measured and the basic optical properties are collected in Table 2. The complete appearance of the UV/vis spectra in a solid thin film are presented in the ESI as Fig. S7.† The absorption maxima of **P-Th** in the film and the solution are nearly at the same positions. This fact indicates a similar conformation of **P-Th** in both solution and solid state. UV/vis spectra of **P-Bt** and **P-Te** in the thin films are more red-shifted than those in solutions. The difference in the absorption maxima between the two states (solid and solution) for **P-Bt** is 14 nm and for **P-Te** it is around 5 nm, indicating that the bithiophene linker is more rigid than the thienothiophene in the **P-Te** unimer. The minor difference between the absorption maxima position in both states confirms a similar conformation and flexibility in solution and solid state.

The solid-state structure of unimers and their MSPs with the Cu^{2+} IC was investigated by powder X-ray diffraction (XRD), allowing insight concerning the crystallinity of the above-mentioned materials. Cu^{2+} was chosen as the best IC leading to the highest shifts of absorption maximum to lower energies ascribable to the formed MSPs (see Table 1). The narrow width of the peaks and the presence of higher order reflections at low angles of **P-Bt** and **P-Te** samples in the XRD patterns indicated the high degree of crystallinity of the unimers studied. XRD patterns of **P-Bt** showed an intense and sharp first-order reflection at a d spacing of 5.7 Å in the 2θ range of 16° (see Fig. 3, and S8 in the ESI†) corresponding to X-ray diffraction patterns of **P-Th**, **P-Te** and their Cu^{2+} based MSPs.

The second most intense peak occurred at $2\theta = 26^\circ$ and corresponded to a d spacing of 3.5 Å. Additionally, the relatively intense presence of reflections with a low intensity but high sharpness in the 2θ range of 15–25° was observed for the **P-Bt** unimer. This detection points to a high degree of crystallinity together with a high rigidity of the conjugated bithiophene linker, which was also confirmed by a UV/vis study of solid thin films. The XRD pattern of **P-Te** showed the two sharpest peaks at $2\theta = 9^\circ$ and 28° , corresponding to a d spacing of 10 Å and 3.3 Å, respectively. As a result, the packaging of **P-Te** is the same as for **P-Bt** unimer. Adversely, the **P-Th** unimer showed a negligible degree of crystallinity. Such observations, together with UV/vis solid-state results for the **P-Th** sample, are caused by less

Table 2 Data of the fluorescence quantum yields (ϕ_F , %) and emission maxima (λ_F) nm of unimers and their Zn-containing MSPs in both states (solution and solid)

State	Unimer						MSP					
	P-Th		P-Bt		P-Te		P-Th + Zn		P-Bt + Zn		P-Te + Zn	
	ϕ_F , %	λ_F nm	ϕ_F , %	λ_F nm	ϕ_F , %	λ_F nm	ϕ_F , %	λ_F nm	ϕ_F , %	λ_F nm	ϕ_F , %	λ_F nm
Solution	12.8	404	7.3	455	14.3	420	22.2	434	34.2	542	17.4	483
Film	1.57	580	1.17	603	1.45	554	2.02	614	1.99	635	1.51	618



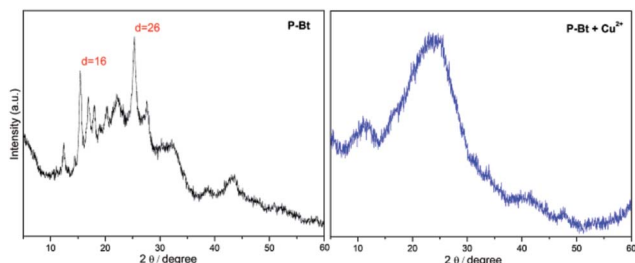


Fig. 3 X-ray diffraction pattern of P-Bt and its Cu^{2+} based MSP. The molar ratio between the unimer and Cu^{2+} is (1 : 1).

ordered configurations. The self-assembled systems, or MSPs, were also included in the XRD analysis. Their diffraction patterns demonstrated a lack of high order reflections in all the unimer based supramolecular systems. Only the broadening of peaks was observed, indicating the amorphous character of the synthesized (MSP)s.

X-ray photoelectron spectroscopy analysis (XPS) was used for the analysis of both free unimers and their MSPs with Cu^{2+} IC. This method was used as an additional tool for the analysis of MSP formations and also for establishing the correct coordination center of the oxazoline moiety (N or O atom). The N1s and O1s XPS spectra of the P-Bt unimer and corresponding Cu^{2+} based MSP are shown in Fig. 4. For all the unimers studied (P-Th, P-Bt and P-Te), a change of position of the peaks in the N1s spectra to a higher binding energy (1.1–2 eV) was observed. This is caused by the electron withdrawing capacity of Cu^{2+} ions, which remove more valence electrons of the nitrogen atoms in

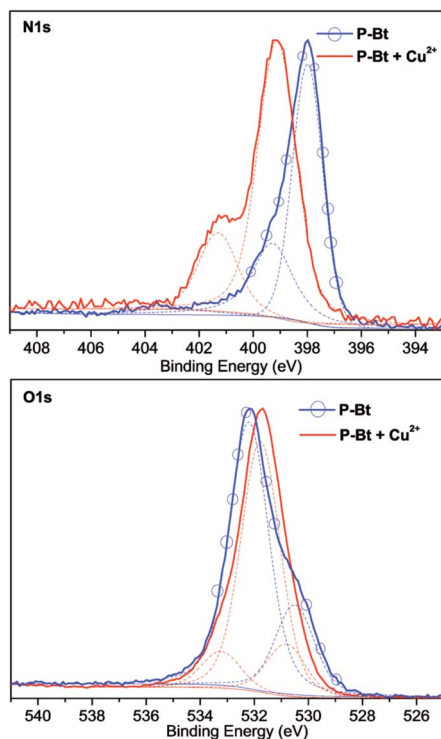


Fig. 4 XPS analysis of P-Bt and corresponding Cu^{2+} based MSP. The molar ratio between the unimer and Cu^{2+} is (1 : 1).

the pyridine and oxazoline groups, resulting in the enhancement of the effective nuclear charge experienced by the core-electron, thereby increasing the electron binding energy. Because the binding energy of O1s electrons changed only slightly (and to a lower binding energy), a predominant coordination of metal ions through the nitrogen atoms can be expected.

UV/vis time-dependent analysis of (MSP)s. An interesting behavior for MSPs containing the Fe^{2+} IC was observed. All the prepared samples for the above-mentioned measurements were left without any treatment for one month in order to check the stability of MSPs formed in solution overtime. In the case of Fe^{2+} we observed a strong degradation of the MSP. The decomposition and loss of properties are independent of the value of r (see Fig. S9b, ESI†). The absorption bands around 630 nm assigned to MLCT totally disappeared. Additionally, the degradation of MSPs could be easily seen by the naked eye. The color of the samples changed from dark green to yellowish brown and gained the same coloration as the free unimers (see Fig. S9 in the ESI†). The remaining MSPs with other ICs (Zn^{2+} , Cu^{2+} , Ni^{2+}) do not degrade even after 1 month. This result for MSPs containing Fe^{2+} is probably caused simply by the oxidation process of the mentioned metal ions. We presume that the Fe^{2+} -containing MSP undergoes constitutional dynamics, causing coordination of the Fe^{2+} IC with only one pybox chelating motif (Fe^{2+} is in the chain end). In this arrangement, Fe^{2+} on the chain-end is probably prone to oxidation (Fe^{3+}). It is worth mentioning that this process is not reversible and all the attempts to restore the Fe^{2+} based MSP to the original state using an excess of ascorbic acid failed. This observation indicates more complex mechanisms for Fe^{2+} based MSP deterioration.

Luminescence study

Analysis of unimers. Fluorescence spectra have been measured in both states (solid thin film and solution) for all the unimers (P-Th, P-Bt, and P-Te). Emission spectra are presented in Fig. S10 in the ESI.† A mixed solvent (chloroform/methanol) (1 : 1) for the preparation of the samples in solution was used. Solid films were prepared by a spin coating method, using the same solvent system. The basic unimer emission characteristics (λ_F (nm) emission maxima and ϕ_F (%) fluorescence quantum yields) are shown in Table 2. The synthesized unimers showed a red shift of emission in solution in the following order: P-Th > P-Te > P-Bt. A deviation from the dependence measured in solution was observed in the thin film, with the following order: P-Te > P-Th > P-Bt. A shift of maximal fluorescence to a longer wavelength (of 50 nm for P-Te and 180 nm for P-Th) was observed. Such a large bathochromic shift in the solid state for P-Th, compared to P-Te and P-Bt, is the result of a lowest substituent hindrance (thiophene-linker) compared to the rest of the unimers, strongly influencing molecular packing in the solid state.

MSP characterization. Titration experiments of the unimers were performed with the above-mentioned ICs. The value of r was increased stepwise (see the Experimental part). The same set of solutions as used for the UV/vis study was used for this



Additionally, new signals close to the main signals of the aromatic moieties appeared and negligible broadening was also observed, indicating the presence of constitutional dynamics in solution.⁴⁸ The second series of signals in the lower magnetic field corresponding to the oxazoline groups also shifted downfield from 4.5 to 4.6 ppm for CH₂O and from 4.06 to 4.12 ppm for CH₂N groups. However, the main changes upon complexation are seen when r is close to unity and a further addition (or increase) of Zn²⁺ IC concentration does not lead to shift changes in the NMR spectra. These results, together with the UV/vis study, revealed that the most stable and probably possessing the longest MSP chains are systems with $r = 1$. Besides that, the formation of MSPs using the **P-Bt** unimer and the Cu²⁺ IC with $r = 1$ was confirmed by a MALDI-TOF study. The mass m/z ($z = 2$) corresponding to the U-IC-U-IC sequence (found for C₆₀Cu₂-H₄₈N₁₂O₈S₄, (658.8)), together with the peaks of different fragments with higher m/z values, indicate the certainty of MSP formation and the presence of high molecular oligomeric sequences that were observed (see Fig. S13, ESI†). Further deciphering of the MALDI-TOF spectrum is nearly impossible (also due to the presence of ClO₄⁻ counterions).



Experimental section

Materials

Tetrabutylammonium bromide, thionyl chloride, 2-chloroethylamine hydrochloride, triethylamine, 1,3-bis(diphenylphosphino)propane nickel(II) chloride [Ni(dppp)Cl₂] (dpp stands for diphenylphosphino-propane), 2,5-bis(trimethylstannyl)thiophene, 5,5'-bis(trimethylstannyl)-2,2'-bithiophene, 2,5-bis(trimethylstannyl)-thieno[3,2-*b*]thiophene, zinc(II) perchlorate hexahydrate, iron(II) perchlorate hydrate, nickel(II) perchlorate hexahydrate, copper(II) perchlorate hexahydrate, (all from Sigma-Aldrich) and 4-hydroxypyridine-2,6-dicarboxylic (chelidamic) acid (**1**), were obtained from commercial sources (Sigma-Aldrich) and used without further purification.

Solvents used for the palladium catalyzed synthesis of unimers and ligands such as toluene and tetrahydrofuran (THF) were dried and distilled by standard methods and stored under argon. Toluene (Lachner) was distilled under argon from sodium/benzophenone prior to use, THF (Aldrich) was distilled from LiAlH₄ before use, methanol (Aldrich), dichloromethane and chloroform (both from Lachner), were used as obtained.

Measurements

¹H and ¹³C NMR spectra were recorded on Varian UNITY INOVA 400 or Varian SYSTEM 300 instruments in CDCl₃, *d*₆-DMSO, CD₃OD and referenced to the solvent signal (δ): 7.25 ppm (CDCl₃), 2.50 ppm (*d*₆-DMSO) or 3.33, 4.78 ppm (CD₃OD) for ¹H and 77.0 ppm (CDCl₃), 49.15 ppm (CD₃OD) ppm for ¹³C spectra. Coupling constants, *J* (in Hz), were obtained by a first-order analysis. UV/vis spectra were recorded on a Shimadzu UV-2401PC using a solvent mixture (CHCl₃/CH₃OH (1/1)) of the prepared compounds. Solid state samples were prepared using coating *via* a slow solvent evaporation technique on the surface of the quartz plate.

Photoluminescence spectra were measured on a Fluorolog 3-22 Jobin Yvon Spex instrument (Jobin Yvon Instruments S. A., Inc., USA) in CHCl₃ + CH₃OH solutions using a four-window quartz cuvette (1 cm). The emission spectra were excited using the wavelength, λ_{ex} , equal to the position of the absorption maxima of a particular compound. Quantum yields, ϕ_{F} , of photoluminescence were measured using an integration sphere Quanta- ϕ F-3029 Horriba Jobin Yvon. X-ray diffraction studies were performed using Bragg-Brentano geometry on a Pan-Alytical X'Pert PRO MPD X-ray diffraction system equipped with a PIXcel detector using a Cu-anode (Cu-K α ; λ = 1.5418 Å). X-ray photoelectron spectroscopy (XPS) measurements were carried out with a K-Alpha⁺ spectrometer (ThermoFisher Scientific, East Grinstead, UK). The samples were analyzed using a micro-focused, monochromated Al K α X-ray source (400 μ m spot size) at an angle of incidence of 30° (measured from the surface) and an emission angle normal to the surface. The kinetic energy of the electrons was measured using a 180° hemispherical energy analyzer operated in the constant analyzer energy mode (CAE) at a 50 eV pass energy for the high resolution spectra. Data acquisition and processing were performed using Thermo Advantage software. XPS spectra were fitted with Voigt profiles

obtained by convolving Lorentzian and Gaussian functions. The analyzer transmission function, Scofield sensitivity factors, and effective attenuation lengths (EALs) for photoelectrons were applied for quantification. EALs were calculated using the standard TPP-2M formalism. All the spectra were referenced to the C1s sp² peak at 284.2 eV. The BE scale was controlled by the well-known positions of the photoelectron C-C and C-H, C-O and C(=O)-O peaks of polyethylene terephthalate and Cu2p, Ag3d, and Au4f peaks of metallic Cu, Ag and Au, respectively. The BE uncertainty of the reported measurements and analysis is in the range of ± 0.1 eV.

SEC records were obtained using a Spectra Physics Analytical HPLC pump P1000 with two SEC columns: Polymer Labs (Bristol, USA) Mixed-D and Mixed-E. The system was equipped with a Thermo UV6000 DAD detector. 0.05 M tetrabutylammoniumhexafluoro-phosphate in CHCl₃/methanol (1/1, v/v, CHROMASOLV, RiedelDeHaen) was used as an eluent (0.7 mL min⁻¹).

Molecular weights of the MSPs were measured by the following method. The raw samples were withdrawn directly from the polymerization mixture and dissolved in a 1/1 chloroform/methanol mixture to a concentration of 1 mg mL⁻¹. Samples were mixed with a matrix solution (saturated solution of 10 mg mL⁻¹ dithranol in 1/1 chloroform/methanol mixture) in a ratio of 1/100 (v/v). 1 μ L of this mixture was deposited on a polished steel MALDI target (Bruker).

Mass spectra of the polymers were measured on an UltrafleXtreme TOF instrument (Bruker), equipped with a 355 nm smartbeam-2 laser, capable of a pulsing frequency of 1 kHz. The mass spectrometer was operated by FlexControl 3.3 software (Bruker). The acquired spectra were processed by FlexAnalysis 3.3 software (Bruker). The ionization laser power was adjusted to just above the threshold in order to produce charged species.

Synthesis of starting materials

Starting compounds dimethyl 4-hydroxypyridine-2,6-dicarboxylate (**2**), dimethyl 4-bromopyridine-2,6-dicarboxylate (**3**), 4-bromopyridine-2,6-dicarboxylic acid (**4**), 4-bromopyridine-2,6-dicarbonyl dichloride (**5**), 4-bromo-*N*²,*N*⁶-bis(2-chloroethyl)pyridine-2,6-dicarboxamide (**6**) and 4-bromo-2,6-bis(4,5-dihydro-2-oxazolyl)-pyridine (**7**) were prepared according to a modified previously reported synthetic procedure.⁴⁹ For more detailed information (synthesis and spectra) see the ESI.[†]

Synthesis of unimers

2,6-Bis(oxazoline-2-yl)-4-(2-thienyl)pyridine (Pybox-Th). Pybox-Th was prepared according to the known above-mentioned procedure (see the ESI[†] for further details). The process of crystallization gave a white solid powder with yield 1.15 g or 72%. ¹H NMR (300 MHz, CDCl₃, ppm) δ 8.33 (s, 2H-pyH, H^{A3}), 7.65 (d, 1H-Th, H^{B2}), 7.47 (d, 1H-Th, H^{B4}), 8.33 (t, 1H-Th, H^{B3}), 4.55 (t, 4H-CH₂N, H^{C2}), 4.14 (t, 4H-CH₂O, H^{C3}). Anal. calculated for C₁₅H₁₃N₃O₂S (*M*_w 29 935 g mol⁻¹), C, 60.19; H, 4.38; N, 14.04; S, 10.71, found: C, 59.87; H, 4.41; N, 14.52; S, 10.45.

2,5-Bis(2,6-bis(4,5-dihydrooxazol-2-yl)pyridin-4-yl)thiophene (P-Th). To a mixture of Pd(PPh₃)₂Cl₂ (0.02 g, 0.03 mmol) and 2,5-bis(trimethylstannyl)thiophene (0.24 g, 0.58 mmol) in freshly



absorption to lower energies, compared to free unimers, was observed for complexation/assembling with the Cu^{2+} IC. Adversely, the lowest shift of the maximal absorption position to lower energies was detected for the Fe^{2+} ion coupler for all the unimers in the studied group, but in this case new bands around 600 nm, ascribable to the metal to ligand charge transfer transition (MLCT), were observed. Complexation of unimers with Zn^{2+} leads to a significant increase in fluorescence intensity, contrary to all the other metals, which showed fluorescence quenching. However, the presence of uncoordinated metal centers in the metallo-supramolecular polymers makes them capable of interacting with certain tridentate monotopic ligands. This confirms the dynamic character of the prepared MSPs (constitutional dynamics between formed MSP chains and free unimer in solution).

Acknowledgements

The authors are grateful to the Czech Science Foundation (project 15-22305S) and the COST Action CM1302 (SIPS) European Network on Smart Inorganic Polymers and the Grant Agency of Charles University (project number 876213 and 796713) for financial support.

References

- absorption to lower energies, compared to free unimers, was observed for complexation/assembling with the Cu²⁺ IC. Adversely, the lowest shift of the maximal absorption position to lower energies was detected for the Fe²⁺ ion coupler for all the unimers in the studied group, but in this case new bands around 600 nm, ascribable to the metal to ligand charge transfer transition (MLCT), were observed. Complexation of unimers with Zn²⁺ leads to a significant increase in fluorescence intensity, contrary to all the other metals, which showed fluorescence quenching. However, the presence of uncoordinated metal centers in the metallo-supramolecular polymers makes them capable of interacting with certain tridentate monotopic ligands. This confirms the dynamic character of the prepared MSPs (constitutional dynamics between formed MSP chains and free unimer in solution).
- ## Acknowledgements
- The authors are grateful to the Czech Science Foundation (project 15-22305S) and the COST Action CM1302 (SIPS) European Network on Smart Inorganic Polymers and the Grant Agency of Charles University (project number 876213 and 796713) for financial support.
- ## References
- 1 J.-M. Lehn, *Supramol. Chem.: Concepts and Perspectives*, VCH, Weinheim, New York, 1995, vol. 8, pp. 89–138.
 - 2 J. L. Atwood, J. E. D. Davies, D. D. MacNicol, F. Vögtle and J.-M. Lehn, *Compr. Supramol. Chem.*, Pergamon, Oxford, 1996, vol. 6, pp. 643–690.
 - 3 J.-M. Lehn, *Makromol. Chem., Macromol. Symp.*, 1993, **69**, 1–17.
 - 4 J.-M. Lehn, *Prog. Polym. Sci.*, 2005, **30**, 814–831.
 - 5 J. Zhang, S. M. Chen and X. H. Bu, *Dalton Trans.*, 2010, 2487–2489.
 - 6 X. Zhao, D. Sun, S. Yuan, S. Feng, R. Cao, D. Yuan, S. Wang, J. Dou and D. Sun, *Inorg. Chem.*, 2012, **51**, 10350–10355.
 - 7 Z. Z. Lu, R. Zhang, Y. Z. Li, Z. J. Guo and H. G. Zheng, *J. Am. Chem. Soc.*, 2011, **133**, 4172–4174.
 - 8 M. Cibian, S. Langis-Barsetti, F. G. D. Mendonça, S. Touaibia, S. Derossi, D. Spasyuk and G. S. Hanan, *Eur. J. Inorg. Chem.*, 2015, **1**, 73–82.
 - 9 V. A. Friese and D. G. Kurth, *Coord. Chem. Rev.*, 2008, **252**, 199–211.
 - 10 M. Chiper, R. Hoogenboom and U. S. Schubert, *Macromol. Rapid Commun.*, 2009, **30**, 565–578.
 - 11 M. Burnworth, L. M. Tang, J. R. Kumpfer, A. J. Duncan, F. L. Beyer, G. L. Fiore, S. J. Rowan and C. Weder, *Nature*, 2011, **472**, 334–338.
 - 12 J. Yuan, X. Fang, L. Zhang, G. Hong, Y. Lin, Q. Zheng, Y. Xu, Y. Ruan, W. Weng, H. Xia and G. Chen, *J. Mater. Chem.*, 2012, **22**, 11515–11522.
 - 13 J. R. Kumpfer and S. J. Rowan, *J. Am. Chem. Soc.*, 2011, **133**, 12866–12874.
 - 14 M. H. Demirel, S. Köytepe, A. Gültek and T. Seçkin, *J. Polym. Res.*, 2014, **21**, 345–355.
 - 15 J. Brassinne, J.-P. Bourgeois, C.-A. Fustin and J.-F. Gohy, *Soft Matter*, 2014, **10**, 3086–3092.
 - 16 J. R. Kumpfer, J. Jina and S. J. Rowan, *J. Mater. Chem.*, 2010, **20**, 145–151.
 - 17 P. R. Andres and U. S. Schubert, *Adv. Mater.*, 2004, **16**, 1043–1068.
 - 18 F. S. Han, M. Higuchi, Y. Akasaka, Y. Otsuka and D. G. Kurth, *Thin Solid Films*, 2008, **516**, 2469–2473.
 - 19 A. Maier, K. Cheng, J. Savych and B. Tieke, *ACS Appl. Mater. Interfaces*, 2011, **3**, 2710–2718.
 - 20 Y. Li, T. Ren and W.-J. Dong, *J. Photochem. Photobiol., A*, 2013, **251**, 1–9.
 - 21 R. Dong, Y. Zhou, X. Huang, X. Zhu, Y. Lu and J. Shen, *Adv. Mater.*, 2014, **27**, 498–526.
 - 22 P. Štenclová, K. Šichová, I. Šloufová, J. Zedník, J. Vohlídal and J. Svoboda, *Dalton Trans.*, 2016, **45**, 1208–1224.
 - 23 J. Svoboda, P. Štenclová, F. Uhlík, J. Zedník and J. Vohlídal, *Tetrahedron*, 2011, **67**, 75–79.
 - 24 T. Vitvarova, J. Zednik, M. Blaha, J. Vohlídal and J. Svoboda, *Eur. J. Inorg. Chem.*, 2012, **2012**, 3866–3874.
 - 25 I. Šloufová, B. Vlčková, M. Procházka, J. Svoboda and J. Vohlídal, *J. Raman Spectrosc.*, 2014, **45**, 338–348.
 - 26 P. Bláhová, J. Zedník, I. Šloufová, J. Vohlídal and J. Svoboda, *Soft Mater.*, 2014, **12**, 214–229.
 - 27 D. Rais, M. Menšík, P. Štenclová-Bláhová, J. Svoboda, J. Vohlídal and J. Pflieger, *J. Phys. Chem. A*, 2015, **24**, 6203–6214.
 - 28 N. B. Shustova, A. F. Cozzolino, S. Reineke, M. Baldo and M. Dinca, *J. Am. Chem. Soc.*, 2013, **135**, 13326–13329.
 - 29 W. H. Zhang, S. W. Chien and T. S. A. Hora, *Coord. Chem. Rev.*, 2011, **255**, 1991–2024.
 - 30 R. Custelcean, J. Bosano, P. V. Bonnesen, V. Kertesz and B. P. Hay, *Angew. Chem., Int. Ed.*, 2009, **48**, 4025–4029.
 - 31 S. Singh, J. Chaturvedi and S. Bhattacharya, *Dalton Trans.*, 2012, **41**, 424–431.
 - 32 E. Menéndez-Pedregal, M. Vaquero, E. Lastra, P. Gamasa and A. Pizzano, *Chem.–Eur. J.*, 2015, **21**, 549–553.
 - 33 C. Friebe, A. Wild, J. Perelaer and U. S. Schubert, *Macromol. Rapid Commun.*, 2012, **33**, 503–509.
 - 34 A. Duerrbeck, S. Gorelik, J. Hobley, J. Wu, A. Hor and N. Long, *Chem. Commun.*, 2015, **51**, 8656–8659.
 - 35 B. M. Paterson and P. S. Donnelly, *Chem. Soc. Rev.*, 2011, **40**, 3005–3018.
 - 36 L. Alibabaei, M. Wang, R. Giovannetti, J. Teuscher, D. D. Censo, J.-E. Moser, P. Comte, F. Pucciarelli, S. M. Zakeeruddin and M. Gratzel, *Energy Environ. Sci.*, 2010, **3**, 956–961.
 - 37 S. N. MacMillan, H. W. Hill and J. C. Peters, *Chem. Sci.*, 2014, **5**, 590–597.
 - 38 T. M. Porter, G. B. Hall, T. L. Groy and R. J. Trovitch, *Dalton Trans.*, 2013, **42**, 14689–14692.
 - 39 F. Czerny, P. Döhlert, M. Weidauer, E. Irran and S. Enthaler, *Inorg. Chim. Acta*, 2015, **425**, 118–123.
 - 40 J. D. Nobbs, A. K. Tomov, R. Cariou, V. C. Gibson, A. J. P. White and G. J. P. Britovsek, *Dalton Trans.*, 2012, **41**, 5949–5964.

- 41 J. Jankowska, J. Paradowska, B. Rakiel and J. Mlynarski, *J. Org. Chem.*, 2007, **72**, 2228–2231.
- 42 P. J. Brown, D. S. Thomas, A. Köhler, J. S. Wilson, J.-S. Kim, C. M. Ramsdale, H. Sirringhaus and R. H. Friend, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2003, **67**, 064203.
- 43 J. K. Stille, *Angew. Chem., Int. Ed. Engl.*, 1986, **25**, 508–524.
- 44 T. Suzuki, T. Sato, J. Zhang, M. Kanao, M. Higuchi and H. Maki, *J. Mater. Chem. C*, 2016, **4**, 1594–1598.
- 45 J. Zhang, C.-Y. Hsu and M. Higuchi, *J. Photopolym. Sci. Technol.*, 2014, **27**, 297–300.
- 46 P. Štenclová-Bláhová, J. Svoboda, I. Šloufová and J. Vohlídal, *Phys. Chem. Chem. Phys.*, 2015, **17**, 13743–13756.
- 47 A. Bremer, U. Müllich, A. Geist and P. J. Panak, *New J. Chem.*, 2015, **39**, 1330–1338.
- 48 T. Vermonden, W. M. de Vos, A. T. M. Marcelis and E. J. R. Sudholter, *Eur. J. Inorg. Chem.*, 2004, **14**, 2847–2852.
- 49 A. De Bettencourt-Dias, S. Viswanathan and A. Rollett, *J. Am. Chem. Soc.*, 2007, **129**, 15436–15437.

