Nanoscale Advances



PAPER

View Article Online
View Journal | View Issue



Cite this: Nanoscale Adv., 2019, 1, 4365

A long-lifespan, flexible zinc-ion secondary battery using a paper-like cathode from single-atomic layer MnO₂ nanosheets†

Yanan Wang,^a Zeyi Wu,^a Le Jiang,^a Wenchao Tian,^a Chenchen Zhang,^b Cailing Cai^a and Linfeng Hu ¹⁰ *

Aqueous zinc ion secondary batteries (ZIBs) have recently attracted considerable attention and global interest due to their low cost, aqueous-based nature and great safety. Unfortunately, the intrinsic properties of poor cycle life, low energy density and uncontrolled dendrite growth during the charge/discharge process for metallic Zn anodes significantly hinder their practical application. In this work, we rationally designed two-dimensional (2D) δ -MnO₂ nanofluidic channels by the ordered restacking of exfoliated MnO₂ single atomic layers, which exhibited a high zinc ion transport coefficient (1.93 \times 10⁻¹⁴ cm² s⁻¹) owing to their appropriate *d*-spacing and the negative charge of the inner channel walls. More importantly, we found that Zn dendrite growth was prevented in the as-assembled ZIBs, resulting in superior stability compared with the bulk-MnO₂ sample. Our design sheds light on developing high-performance ZIBs from two-dimensional nanofluidic channels, and this strategy might be applicable to the storage of other metal ions (Mg²⁺, Ca²⁺, Al³⁺, etc.) in next-generation electrochemical energy storage devices.

Received 20th August 2019 Accepted 23rd September 2019

DOI: 10.1039/c9na00519f

rsc.li/nanoscale-advances

1. Introduction

Owing to the high abundance of zinc, high theoretical capacity (820 mA h g^{-1}), low electrochemical potential (-0.762 V versus the standard hydrogen electrode (SHE)), intrinsic safety and environmental friendliness, zinc ion rechargeable batteries (ZIBs) with mild aqueous electrolytes have attracted considerable attention and global interest.1-6 Nevertheless, it is still at an initial stage for ZIBs and their reported electrochemical performance has still remained far from practical requirements. The main challenges should be attributed to Zn dendrite formation during charge/discharge cycling. Similar to many other metals such as Li, Ni and Cu, zinc generally tends to deposit in the dendrite form especially at high current densities, which results in low coulombic efficiency, rapid degradation of capacity and poor stability. More seriously, the needlelike Zn dendrites may puncture the separator, leading to short circuits and safety concerns.7,8

Theoretically, the origin of dendrite growth can be ascribed to the metal-ion concentration gradient and tip effect during electroplating. 9-12 In general, the depletion of metal ions in the electrolyte caused by the concentration gradient breaks the

electrical neutrality at the plated electrode surface, leading to a local space charge and ramified Zn electro stripping/plating on the screw dislocations of the Zn surface.13 Extensive efforts have been devoted to solving the dendrite growth problem in ZIBs. 14,15 Typical strategies, such as constructing Zn anodes with a hierarchical architecture and preparing a composite Zn anode coating as a thin inert layer to stabilize the Zn anode, have been developed to suppress dendritic growth in ZIBs.16 Most recently, Wang et al. achieved great progress on dendrite-free plating/ stripping of Zn in a highly concentrated Zn(TFSI)2 electrolyte with a supporting salt of LiTFSI (bis(trifluoromethanesulfonyl) imide).17 Nevertheless, either the complicated fabrication process of the inert layer or the high cost of the highly concentrated Zn-ion electrolyte hinders widespread application and industrial production. Thus, it is still highly desirable to design a new strategy to realize dendrite-free ZIBs with excellent reversibility and stability.

Two-dimensional (2D) nanostructures with a single-atomic layer thickness have attracted intensive attention for the development of energy-storage devices because of the emergence of novel physical and chemical properties which are distinct from those of or even absent in their bulk counterparts. In particular, 2D nanostructure units are rather soft and flexible and have been considered ideal building blocks of freestanding, flexible membrane samples as high-performance electrodes. Such freestanding electrodes are completely composed of 2D active materials without any current collectors and polymer binders, leading to a superior performance due to

[&]quot;Department of Materials Science, Fudan University, Shanghai 200433, China. E-mail: linfenghu@fudan.edu.cn

^bState Grid Anhui Electric Power Institute, Hefei, 230022, China

 $[\]dagger$ Electronic supplementary information (ESI) available: Supplementary tables and figures. See DOI: 10.1039/c9na00519f

the unique structure and significantly decreased interfacial resistance.²⁴ More importantly, such a restacked structure in the freestanding, flexible membrane fabricated from the 2D building blocks could produce lamellar nano-channels and atomically smooth surfaces for nanofluids such as liquid or quasi solid-state electrolytes.^{25,26} It has been verified that 2D nanochannels obtained by exfoliation and restacking of layered compounds are ideal frameworks for fast Li-ion storage because of their abundant interconnected (horizontal and vertical) channels, large active surface and short diffusion path.²⁷

Most recently, flexible ZIBs based on binder-free α-MnO₂ nanosheets/rGO on carbon cloth have been realized.28 However, the \alpha-MnO2 nanosheets in this work were synthesized by a hydrothermal route and their thickness is much larger than the single layer thickness. The resulting α-MnO₂ nanosheets/ rGO thin-film generally exhibits a rough surface and a loose, overlapping structure with the absence of 2D nanochannel characteristics. We note that the recent advances in layered-MnO₂ demonstrate that it can be exfoliated into 2D negatively charged nanosheets with single-atomic layer thickness by a softchemical strategy.^{29,30} Is it possible to construct unique 2D nanochannels with controllable interlayer spacing from these 2D building blocks? What would happen in these 2D nanofluidic channels for Zn²⁺ transport? It would be of great interest to study the performance of ZIBs constructed from such freestanding nanochannels and further understand the Zn2+ storage mechanism.

Inspired by this consideration, herein, we demonstrate a proof-of-concept strategy to construct 2D nanofluidic channels from liquid-exfoliated MnO₂ single-layer nanosheets (Fig. 1). The as-constructed paper-like Zn ion battery from these nanofluidic channels exhibited excellent flexibility and a high

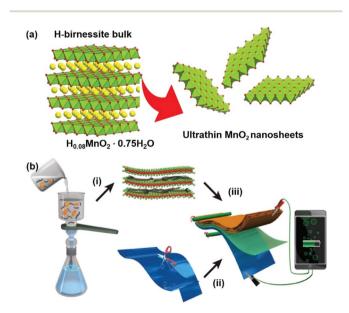


Fig. 1 (a) Crystal structure evolution by liquid exfoliation of the H-birnessite bulk into single-atomic layers. (b) Schematic illustration of (i) the vacuum-assisted filtration strategy to fabricate the freestanding $\rm MnO_2/MWCNT$ hybrid membrane; (ii) trimmed zinc foil as the anode material; (iii) assembly of a proof-of-concept paper-like ZIB.

energy density up to 365 W h kg⁻¹. We found that Zn dendrite growth was prevented in the paper-like ZIBs, resulting in superior stability compared with batteries based on a bulk-MnO₂ cathode. Our design sheds light on developing high-performance ZIBs from two-dimensional nanofluidic channels, and this strategy might be applicable to storage of other metal ions (Na⁺, Mg²⁺, Ca²⁺, Al³⁺, etc.) in next-generation electrochemical energy storage devices.³¹⁻³⁴

2. Experimental section

2.1 Preparation of the H_{0.08}MnO₂·0.75H₂O precursor

Potassium permanganate (KMnO₄, GR, 6 mmol, Sinopharm Chemical Reagent Co. Ltd (SCRC)) was dissolved in 137.5 mL Milli-Q water (18.2 M Ω cm) to form a purple solution, and potassium hydroxide (KOH, AR, 3 mol, SCRC) was added to this solution in two batches under stirring at 400 rpm and then mixed with 20 mL of a manganese(II) chloride tetrahydrate (MnCl₂·4H₂O, AR, 0.6 M, SCRC) aqueous solution and stirred for 2 h to obtain a uniform precursor solution. This solution was hydrothermally treated at 175 °C for 3 days. The manganese oxide precipitate was washed with Milli-Q water 4 times to neutral pH, after which ammonium persulfate ((NH₄)₂S₂O₈, AR, 0.25 mol, SCRC) and the neutral solution were added into a three-necked flask at 60 °C for 3 h (repeated 3 times) and then filtered and washed with Milli-Q water and finally dried in air at room temperature. The ideal reaction mechanism of the synthesis is:

 $K_{0.33}MnO_2 \cdot 0.47H_2O + (NH_4)_2S_2O_8 \rightarrow H_{0.08}MnO_2 \cdot 0.75H_2O$

2.2 Exfoliation

For the exfoliation process, the as-synthesized $H_{0.08}MnO_2 \cdot 0.75H_2O$ (0.36 g) and tetramethylammonium hydroxide (TMAOH, 10.4 mL, Aladdin) were dispersed into 80 mL Milli-Q water. The as-obtained suspension was shaken for 24 h at 100 rpm and washed with Milli-Q water to neutral pH by the centrifugation (6000 rpm for 10 min) method. Subsequently, a further peeling-off process was implemented, in which the as-obtained suspension and tetrabuty-lammonium hydroxide (TBAOH, 0.74 mL, Aladdin) were dispersed into 90 mL Milli-Q water and then shaken for 72 h at 80 rpm to obtain exfoliated MnO₂ nanosheets.

2.3 Preparation of the MnO₂/MWCNT membrane

The as-obtained exfoliated MnO_2 nanosheet suspension (\sim 40 mmol L^{-1}) was mixed with carbon nanotubes (industrial multi-walled carbon nanotubes (MWCNTs-010-0), Tanfeng Technology Co., Ltd) and an *N*-methylpyrrolidone (NMP, AR, SCRC) solution (0.5 mg mL⁻¹) at a volume ratio of 1:2 by mechanical grinding for 10 minutes and ultrasonic dispersion for 30 minutes. The $MnO_2/MWCNT$ membrane was prepared by vacuum filtering the obtained suspension, washing it with Milli-Q water 3 times and drying it under ambient conditions for 3 days. The loading mass of MWCNTs on the $MnO_2/MWCNT$ membrane was around 20%. The mass density of $MnO_2/MWCNT$ electrodes was \sim 0.96 g cm⁻³.

Paper Nanoscale Advances

2.4 Preparation of the δ-MnO₂ bulk

The δ -MnO $_2$ bulk sample was obtained by heating KMnO $_4$ powder in an air atmosphere at 350 °C for 5 h and cooling naturally. The powder product was washed with Milli-Q water 3 times and dried at 80 °C for 12 h and finally thoroughly ground. The ZIB cathode made of the δ -MnO $_2$ bulk was prepared according to the following process: active powder: Ketjen black: poly(vinylidene fluoride) (PVDF) (mass ratio: 7:2:1) was mixed homogeneously, and then the slurry mixture was coated onto 304 stainless steel foil and dried under vacuum at 120 °C for 12 h. Then the stainless steel foil after coating was punched into circular pieces (d=15 mm, mass density: 1.1 g cm $^{-3}$) for the assembly of coin-type cells.

2.5 Characterization

The tensile strength of the MnO₂/MWCNT membrane was measured using an AUTO tensile tester (Labthink, XLW (PC)). A field emission scanning electron microscope (FE-SEM, FEI Nova Nano SEM 450) and an atomic force microscope (AFM, Bruker Dimension Icon) were used to characterize the sample's morphology. X-ray photoelectron spectroscopy (XPS, PerkinElmer PHI 5000C ESCA, with Mg Kα radiation, standard signal: C 1s peak 284.6 eV) analysis was performed to investigate the elemental distribution and chemical components. X-ray powder diffraction (XRD) analysis was performed to investigate the crystal structure (Bruker D8-A25 diffractometer using Cu K α radiation ($\lambda = 1.5406 \text{ Å}$), the scan rate was $2^{\circ} \text{ min}^{-1}$). Thermogravimetric (TG) analysis combined with differential scanning calorimetry (DSC, SDT Q600, the heating rate was 10 °C min⁻¹ and the air flow was 50 mL min⁻¹) was adopted to explore the sample's thermal behavior. Transmission electron microscopy (TEM) and selected area electron diffraction (SAED) were performed using a Philips CM 200 FEG field emission microscope. A zeta-potential tester (Zetasizer Nano ZS90) was used to characterize the surface charge state of the nanosheets dispersed in solvents.

2.6 Electrochemical measurements

The electrochemical performances of the assembled coin-type MnO₂/MWCNTs//zinc and MnO₂ bulk//zinc unit cells, such as the discharge capacity, discharge C-rate capability, and cycling performance, were evaluated using a LAND battery cycle system (Wuhan LAND Electronics Co., LTD, China) in the voltage range of 1.0-1.9 V under ambient conditions. For the MnO₂/ MWCNTs//zinc paper-like battery, the MnO₂/MWCNT cathode and the high purity zinc foil (thickness of 30 µm, Tengfeng Metal Materials LTD) were punched into circular pieces (d = 15mm), Whatman glass fiber (GF, thickness of 350 µm) was used as the separator, and a mixture of zinc sulfate (ZnSO₄·7H₂O₇) 99.995%, 2 M, SCRC) and manganese sulfate (MnSO₄·H₂O, AR, 0.2 M, SCRC) aqueous solutions was used as the electrolyte. The charge and discharge cycling performance of the cells was measured at 0.1 A g^{-1} for 600 cycles and the C-rate capability of the cells was examined from 0.1 A g⁻¹ to 2 A g⁻¹. Cyclic voltammetry (CV) and electrochemical impedance analysis of the

 $\rm Zn^{2+}/Zn$ unit cells were performed on an electrochemical workstation (CHI660e) over the frequency range of 10 mHz to 1 MHz. The performance (energy and power densities) was estimated based on the weight of the active MnO₂ only.

3. Results and discussion

Negatively charged MnO₂ single-atomic layer nanosheets were prepared by a liquid-exfoliation strategy from the H-birnessite bulk.27 A dark-brown colloidal suspension was obtained with a high concentration (~40 mmol L⁻¹) of the MnO₂ nanosheets in the water phase (Fig. 2a). Clear Tyndall light scattering of the colloidal suspension was observed in a diluted nanosheet suspension (Fig. 2b). Their negative surface charge was proven by the negative zeta potential measurement (-32 mV, Fig. S1, ESI†). Atomic force microscopy (AFM) characterization revealed a typical 2D nanosheet morphology with average lateral dimensions of 1-1.5 µm (Fig. 2c) and a thickness of 1.0 nm (Fig. 2d and e). Note that the theoretical thickness of the MnO₂ single-layer nanosheets is estimated to be 0.52 nm. The measured thickness is slightly larger than the theoretical thickness by approximately 0.4 nm, which might be due to the distance between the substrate and MnO2 as well as between MnO2 and the probe. This phenomenon has been observed in a previous study.³⁰ The transmission electron microscope (TEM) image also shows ultrathin sheet-like objects with lateral dimensions similar to those observed in the AFM image (Fig. S2, ESI†).

The ultrathin nature, nanosheet-like morphology and inherent flexibility are quite promising for constructing freestanding membranes by a facile vacuum-assisted filtration

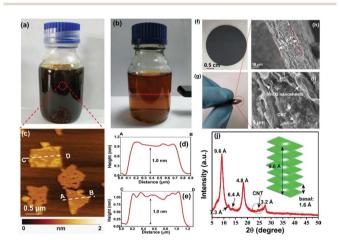


Fig. 2 (a and b) Photograph of exfoliated MnO₂ nanosheets dispersed in Milli-Q water at high and low concentrations, respectively. The Tyndall effect was observed in the diluted solution. (c) Typical AFM image of the MnO₂ nanosheets. (d and e) The height profile along the dashed line in (d). (f and g) The photographs show the MnO₂/MWCNT membrane with high flexibility. (h and i) Typical cross-sectional SEM images of the membrane. (j) XRD pattern of the hybrid film. A weak diffraction peak with a d-spacing of 7.3 Å was described in Liu's work for aggregated nanosheets centrifuged from the mixture of H-birnessite and TBAOH.³⁰ The characteristic, broad peak of MWCNTs was detected at $2\theta = 26^{\circ}$.

Nanoscale Advances Paper

strategy. In order to improve the electronic conductivity of this membrane, we consider the incorporation of conductive multiwalled carbon nanotubes (MWCNTs) into this membrane sample. Mixing the two colloidal solutions of MnO₂ nanosheets and MWCNTs with sonication for an additional 30 min produces a homogeneous dispersion with no apparent precipitation. Then, a hybrid, black MnO₂/MWCNT membrane was easily fabricated by the vacuum-assisted filtration strategy with a lateral size of 4 cm (Fig. 2f). The as-obtained membrane is highly flexible (Fig. 2g), and it can be freely rolled up by hand and using glass rods (Fig. S3, ESI†). The optimal mass ratio of MWCNTs in the composite $MnO_2/MWCNT$ membrane is $\sim 20\%$ because a high concentration of MWCNTs over this threshold can drastically decrease the flexibility of the hybrid membrane. The top-view SEM image shows a rather smooth and dense surface of our MnO₂/MWCNTs membrane (Fig. S5, ESI†), which is completely different from the loose, rough structure in the previous work.25 The cross-sectional SEM image in Fig. 2h suggests that the thickness of this freestanding membrane is \sim 33 µm. One can see the densely stacked structure with abundant 2D nanofluidic channels in the cross-section of this membrane (Fig. 2i). X-ray photoelectron spectroscopy (XPS) analysis also confirms the existence of Mn, O, and C elements in this hybrid membrane (Fig. S6, ESI†). The formation of welldefined 2D nanofluidic channels was further confirmed by Xray diffraction (XRD) characterization (Fig. 2j), which exhibits a series of intense and sharp (00l) diffraction peaks with a dspacing of 9.6 Å, 6.4 Å, 4.8 Å, and 3.2 Å, respectively. This result indicates a basal spacing of 1.6 Å with preferred orientation and ordered stacking along the [010] direction during the vacuumassisted filtration process, and this is well consistent with that of the MnO₂/MXene hybrid membrane.³⁵ The preferred orientation of these restacked nanosheets results in ideal 2D nanofluidic channels with atomically smooth surfaces as highly expected.

The thermal stability of the $MnO_2/MWCNT$ membrane was further evaluated by thermogravimetric analysis (TGA), which showed that our $MnO_2/MWCNT$ membrane was thermally stable up to 225 °C (Fig. S7, ESI†). We further checked the wettability of our $MnO_2/MWCNT$ membrane in the as-employed 2 M $ZnSO_4/0.2$ M $MnSO_4$ aqueous electrolyte for ZIB applications. This $MnO_2/MWCNT$ membrane is hydrophilic with an initial contact angle of 18.7°, and this contact angle gradually decreased to 5.2° in a short time of ~ 15 seconds (Fig. S8, ESI†). The rapid decrease in contact angle may provide evidence of the facile permeation and transfer of the aqueous electrolyte in our $MnO_2/MWCNT$ membrane.³⁶

Based on the successful formation of 2D nanofluidic channels, the electrochemical properties of the $MnO_2/MWCNT$ membrane cathode were subsequently measured in a typical coin-type cell. Fig. 3a shows the CV profile of the $MnO_2/MWCNT$ membrane cathode at 0.05 mV s $^{-1}$, and two redox peaks at 1.42 V and 1.30 V were detected. Fig. 3b shows the cyclic voltammograms (CVs) of this membrane sample in an aqueous 2 M ZnSO $_4/0.2$ M MnSO $_4$ electrolyte within the coin-type cell. Our CV curves are mostly consistent with those of the $\delta\text{-MnO}_2$ bulk electrode in the previous study. 37 Two cathodic peaks

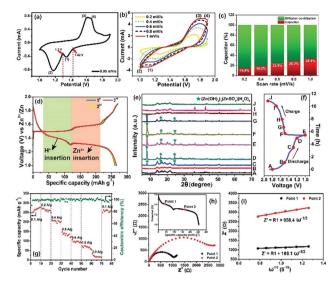


Fig. 3 (a) CV profile of the MnO₂/MWCNT membrane cathode at a slow scanning rate of 0.05 mV s⁻¹. (b) CV profile of the MnO₂/MWCNT membrane cathode at 0.2–1.0 mV s⁻¹. (c) The capacitive contribution (red region) to the total current at various scan rates. (d) Characteristic galvanostatic charge/discharge profile of the MnO₂/MWCNTs in the initial cycles. (e and f) *Ex situ* XRD pattern of the δ -MnO₂/MWCNT cathode at various discharge/charge states. (g) Rate capability. (h) Nyquist spectrum measured at the corresponding point on the discharge curve (inset) for Zn²⁺ diffusion coefficient analysis. (i) Z' vs. $\omega^{-1/2}$ plots in the low frequency region obtained from the electrochemical impedance spectroscopy measurements.

located at 1.35 eV and 1.17 eV can be observed, which are attributed to Zn^{2+} insertion into the restacked δ -MnO $_2$ nanosheets and the consequent reduction of Mn^{4+} to lower oxidation states, respectively. The appearance of an overlapped anodic peak at around 1.70 V may correspond to Zn-extraction which is accompanied by the recovery to the Mn(ν) state. We further estimate the pseudocapacitance-like contribution by clarifying the kinetics to separate the capacitive-controlled and diffusion-controlled capacities. In general, the capacitive contribution can be quantified using the modified power law: 38

$$I = I_{\text{capacitive}} + I_{\text{diffusion}} = k_1 \nu + k_2 \nu^{1/2}$$
 (1)

where I is the current; ν is the scan rate; $k_1\nu$ and $k_2\nu^{1/2}$ correspond to the current contributions from the pseudocapacitive effect and diffusion-controlled insertion, respectively (Fig. S10, ESI†). The typical CV profile in Fig. 3b separates the capacitive current (red region) from the diffusion current (green region). The contribution of capacitive current is 14.4%, 18.2%, 23.9%, 28.3% and 33.4% at scan rates of 0.2, 0.4, 0.6, 0.8 and 1.0 mV s⁻¹ (Fig. 3c), respectively. Fig. 3d depicts the characteristic galvanostatic charge/discharge profile of the MnO2/MWCNT membrane electrode in the initial three cycles. Two discharge plateaus at 1.42 V and 1.30 V should be ascribed to H^+ and Zn^{2+} insertion and extraction, respectively. In general, these two discharge plateaus were easily observed in manganese oxidebased ZIBs due to the coexistence of the reversible Zn ion insertion/extraction and proton reaction during the electrochemical process as follows:39

Paper Nanoscale Advances

$$MnO_2 + xZn^{2+} + 2xe^- \leftrightarrow Zn_xMnO_2 \cdot xH_2O, (0 < x < 1)$$
(Zn ion insertion/extraction)

$$MnO_2 + H^+ + e^- \leftrightarrow MnOOH$$
 (proton reaction)

$$4Zn^{2+} + 6OH^{-} + SO_{4}^{2-} + 5H_{2}O \leftrightarrow 3Zn(OH)_{2} \cdot ZnSO_{4} \cdot 5H_{2}O$$

To further understand the phase evolution more clearly, ex situ XRD characterization of this freestanding membrane was performed as shown in Fig. 3e and f. Notably, the XRD pattern at the initial discharging state (A) was drastically different from that of the fresh MnO₂/MWCNT membrane just after vacuum filtration (Fig. 2n), which was also reported by T. Vaughey.40 During the following discharging process (A \rightarrow E), the diffraction peaks significantly decreased in intensity, and some sharp peaks (including sharp peaks at 7.9°, 16.2°, and 24.2° and other weak peaks highlighted by grey cycles) emerged when it was discharged to 1.3 V, which can be indexed to 3Zn(OH)2-·ZnSO₄·5H₂O (zinc hydroxide sulfate hydrate, JCPDS 78-0246).³⁹ The formation of zinc hydroxide sulfate hydrate should be attributed to the increasing amount of OH groups in the electrolyte, further confirming the reversible proton reaction.41 During the subsequent charging process (E \rightarrow J), the diffraction peaks from the intermediate phase of zinc hydroxide sulfate hydrate gradually disappeared, and the pattern finally well recovered to the initial state (A) when the charge voltage was 1.6 V (H). In general, the ex situ XRD characterization clearly confirms the excellent reversibility of the Zn2+ intercalation/ deintercalation process in our MnO2/MWCNT membrane. The rate capability of the MnO2/MWCNT electrode in the range of 1-1.9 V is evaluated at various current densities (0.1-2 A g⁻¹) (Fig. 3g). The MnO₂/MWCNT electrode shows high reversible capacities of 273.8, 265.1, 206.8, 135.5, 99, 71.4 and 20.3 mA h g⁻¹ at current densities of 0.1, 0.2, 0.4, 0.6, 0.8, 1 and 2 A g⁻¹, respectively (Fig. S11, ESI†). When the current density is decreased back to 0.1 A g-1, the capacity returns to 270.2 mA h g⁻¹, demonstrating its outstanding capacity retention at both low and high rates.

It has been revealed that the electrolyte ions show drastically different behavior when confined in 2D nanochannels.22-24 Subsequently, the Zn²⁺ diffusion ability in our δ-MnO₂/MWCNT membrane was identified using electrochemical impedance spectroscopy (EIS). Combining the Nyquist spectra measured at the first (Point 1) and second (Point 2) discharge depth (Fig. 3h) and Z' vs. $\omega^{-1/2}$ plots (Fig. 3i), the diffusion coefficient can be calculated based on the following equation: 42,43

$$D = \frac{R^2 T^2}{2A^2 n^4 F^4 C^2 \sigma^2} \tag{2}$$

where R, T, and F are the gas constant (8.314 J K^{-1} mol⁻¹), the experimental temperature (298 K), and the Faraday constant (96, 500 C mol^{-1}), respectively. A is the surface area of the electrode, n is the number of electrons per molecule taking part in the electronic transfer reaction, C is the concentration of inserted ions in MnO₂/MWCNTs, and σ is the slope of the line Z' vs. $\omega^{-1/2}$. The calculated diffusion coefficients of the proton (H⁺) and Zn-ion platform are as high as 1.49×10^{-12} (the first

discharge platform) and 1.93 \times 10⁻¹⁴ cm² s⁻¹ (the second platform), respectively, which are comparable with the highest values in the recent reports on MnO2 cathodes for ZIBs.32 As a comparison, the δ-MnO₂ bulk with irregular morphology was prepared via thermal decomposition of KMnO₄ similarly to Kim's route³⁰ (Fig. S12, ESI†). The MnO₂ bulk sample shows smaller values of proton and Zn-ion diffusion coefficients of 3.63×10^{-13} and 1.56×10^{-14} cm² s⁻¹, respectively (Fig. S13, ESI†). Such a high Zn²⁺ diffusion coefficient should be attributed to the advantages of our 2D δ-MnO₂ nanofluidic channels: (i) the incorporated MWCNTs (as both the spacer and the conductive enhancer) play a crucial role in the fast charge diffusion kinetics due to their highly disordered porous structure, and the channels in the vertical direction were crosslinked with the incorporated MWCNTs for enhanced Zn ion migration; (ii) the MnO₂ nanosheets exfoliated from the H_{0.08}-MnO₂·0.75H₂O bulk generally show a strongly negatively charged surface, and our MnO2 nanofluidic channels contain abundant horizontal and vertical pathways for Zn²⁺ transport. We theoretically compare the Debye length of Zn^{2+} with the interlayer spacing of the horizontal pathway. In principle, the value of the Debye length (λ_D) can be calculated using:⁴⁴

$$\lambda_{\rm D} = \frac{3.04 \times 10^{-10}}{z_{\rm i} \sqrt{c_{\rm i}}} \tag{3}$$

where z_i and c_i are the valency and concentration of Zn^{2+} , respectively. In our work, a 2 M ZnSO₄/0.2 M MnSO₄ aqueous solution was employed as the electrolyte. Thus, the Debye length is estimated to be 0.11 nm. Note that the d-spacing (0.96) nm) of restacked δ-MnO2 nanofluidic channels determined from the XRD pattern (Fig. 2n) is larger than the value of the Debye length, showing the same tendency as the Co₃O₄ nanochannels in Li ion storage reported by Yu et al. 23 Accordingly, inside our 2D nanochannel, when the characteristic dimensions are comparable or less than the Zn²⁺ Debye length (0.11 nm), the negative MnO2 surface charges on the inner walls would repel counterions of the same charge (negative SO₄²⁻ groups), making Zn²⁺ the dominating charge carriers.^{25,45} This unipolar ionic transport is generally beneficial for high Zn²⁺ conductivity and a high diffusion coefficient.22,23

More attention has been paid to the long-term cycle performance of this MnO₂/MWCNT membrane. Our δ-MnO₂ membrane-like cathode delivers a capacity of 273.8 mA h g^{-1} for 600 cycles with a coulombic efficiency around 100%. In contrast, the δ-MnO₂ bulk counterpart displays rather poor cycling stability, the capacity of which drastically faded after the initial 10 cycles (Fig. 4a and S14, ESI†). In general, the formation of needle-like Zn dendrites on the Zn anode should be the main reason for the rapid degradation of capacity and poor stability.7 Thus, the reason for the difference in stability of our MnO₂/ MWCNT membrane was further studied by SEM observation of the Zn foil anode after long-term cycling. Interestingly, one can clearly see that the Zn foil taken from the δ-MnO₂ bulk ZIBs shows a rough surface with dense Zn dendrites (Fig. 4b). However, the δ-MnO₂/MWCNT membrane based ZIBs show a typical dendrite-free surface (Fig. 4c) with the absence of any ZnO by-products on the Zn foil after 600 charge/discharge cycles

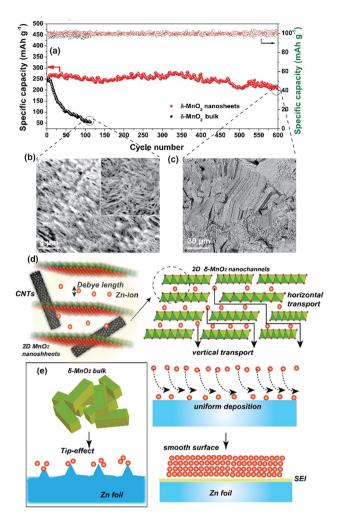


Fig. 4 (a) Cycle performance and coulombic efficiency of the MnO₂-based ZIBs in a voltage range of 1.0–1.9 V at 0.1 A g⁻¹. SEM images of the Zn foil anode surface morphology in the (b) δ -MnO₂ bulk and (c) flexible MnO₂/MWCNT ZIBs after 600 cycles. Schematic illustration of the Zn²⁺ transport process in (d) 2D nanofluidic channels and (e) the δ -MnO₂ bulk, respectively.

(Fig. S15, ESI†). Although the origin of the dendrite-free characteristics in the membrane-based battery is not yet clear, we speculate that the smooth surface in our advanced 2D channel structure may be responsible. Recently, Liaw et al. found that the inhomogeneity of the distribution of the current density increases with the increase of the cathode particle size and surface roughness.12 In our case, taking advantage of the characteristic 2D planar morphology with a high aspect ratio, the nanosheets are generally tiled on the filter paper during the vacuum filtration process. As a result, there are almost no MWCNTs on the outermost surface of the MnO₂/MWCNT membrane (Fig. 2i and S5†). Such a smooth surface of the MnO₂/MWCNT membrane cathode could significantly reduce the concentration gradient in the electrolyte and induce homogeneous Zn²⁺ stripping/plating on the zinc anode (Fig. 4d). In contrast, for the bulk MnO₂ cathode, the sharp corners and irregular morphology of the bulk MnO₂ gives rise to the tip-effect with a high concentration gradient during the Zn²⁺ stripping/plating process (Fig. 4e). Finally, dense Zn dendrite growth occurred at the surface of the Zn foil, drastically decreasing the cycling stability of the battery system.⁷⁻⁹

We finally assembled a sandwiched, paper-like ZIB using the δ -MnO₂ membrane, a 2 mol L⁻¹ ZnSO₄ + 0.2 mol L⁻¹ MnSO₄ solution, PET non-woven fabric (thickness $\sim 80 \, \mu m$) and flexible Zn foil as the cathode, electrolyte, separator and anode, respectively (Fig. 5a). This paper-like battery shows a thickness of just \sim 132 µm (Fig. 5b) which is comparable with that of standard A4 printing paper (Fig. 5c). Two paper batteries connected in series were able to light up a red light-emitting diode (LED) indicator (Fig. 5d). The flexibility of this battery was tested by bending this device at various angles from 45° to 180°, while well maintaining the same energy storage characteristics as those in the initial state (Fig. 5d-i, ESI Video 1†). Compared to a single paper-like ZIB with a charge/discharge potential of 1.4 V, two ZIBs connected in series can achieve 2.8 V in a similar charge/discharge time (Fig. 5j). The flexible ZIB delivers a capacity of 181.6 mA h g⁻¹ for 630 cycles at 0.5 A g⁻¹ (Fig. S16†). The energy density and power density are 365 W h kg⁻¹ and 105 W kg⁻¹ (estimated based on the weight of the active MnO2 only), respectively. Such a high energy density surpasses not only that of recently reported MnO₂-based ZIBs, but also that of other V-based and HCF-based counterparts (Fig. 5k).37,41,46-53

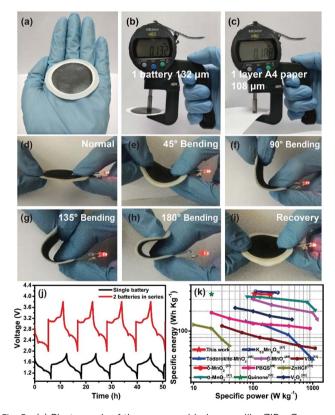


Fig. 5 (a) Photograph of the as-assembled paper-like ZIBs. Comparison between the thickness of (b) the membrane-like ZIBs and (c) standard A4 printing paper. (d-i) The flexible membrane-battery powers a red LED indicator at various bending angles. (j) Galvanostatic charge/discharge curves of a single battery and two batteries connected in series at $0.05A\ g^{-1}$. (k) Ragone plot related to energy and power densities of recently reported ZIBs and the present work.

Paper

Conclusions 4.

In summary, we have successfully constructed 2D MnO₂ nanofluidic channels by the restacking of abundant single-layer δ-MnO₂ nanosheets. Compared to the δ-MnO₂ bulk, our 2D MnO₂ nanofluidic channels show fast Zn2+ transport and superior cycling stability. The high-performance of Zn²⁺ storage in our rationally designed nanofluidic channels should be associated with the following merits: (1) 2D nanochannels provide abundant interconnected ion transport pathways in vertical and horizontal directions to make the Zn²⁺ flow uniform, preventing the tip-effect and dendrite formation during Zn ion deposition. (2) The implantable MWCNTs play a crucial role in the fast charge diffusion kinetics due to their highly disordered porous structure, and the channels in the vertical direction were crosslinked with the implantable MWCNTs for enhanced Zn ion migration. (3) The void space inside the nanofluidic channels may effectively alleviate structural stress and buffer the volume change during the Zn²⁺ insertion/extraction, avoiding the rapid decay of specific capacity of the ZIBs during cycling caused by irreversible structural collapse of the cathode. (4) Our freestanding δ-MnO₂/MWCNT membrane does not contain any polymer or insulating binder which will avoid sacrificing the active substance content in the ZIBs, thereby achieving enhanced specific capacity after normalization when compared to the conventional δ-MnO₂ bulk electrodes. Our design sheds light on developing high-performance ZIBs from twodimensional nanofluidic channels, and this strategy might be applicable to storage of other metal ions (Mg²⁺, Ca²⁺, Al³⁺, etc.) in next-generation electrochemical energy storage devices.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the Research Program of State Grid Corporation of China (GYW17201800011).

References

- 1 E. Hu and X.-Q. Yang, Nat. Mater., 2018, 17, 480.
- 2 G. Fang, J. Zhou, A. Pan and S. Liang, ACS Energy Lett., 2018, 3, 2480.
- 3 L. Ma, S. Chen, H. Li, Z. Ruan, Z. Tang, Z. Liu, Z. Wang, Y. Huang, Z. Pei, J. A. Zapien and C. Zhi, Energy Environ. Sci., 2018, 11, 2521.
- 4 H. Li, C. Han, Y. Huang, Y. Huang, M. Zhu, Z. Pei, Q. Xue, Z. Wang, Z. Liu, Z. Tang, Y. Wang, F. Kang, B. Li and C. Zhi, Energy Environ. Sci., 2018, 11, 941.
- 5 S. Guo, G. Fang, S. Liang, M. Chen, X. Wu and J. Zhou, Acta Mater., 2019, 180, 51.
- 6 F. Liu, Z. Chen, G. Fang, Z. Wang, Y. Cai, B. Tang, J. Zhou and S. J. N.-M. L. Liang, Nano-Micro Lett., 2019, 11, 25.
- 7 D. Lin, Y. Liu and Y. Cui, Nat. Nanotechnol., 2017, 12, 194.

- 8 Z. Xing, S. Wang, A. Yu and Z. Chen, Nano Energy, 2018, 50, 229.
- 9 J.-l. Ma, F.-l. Meng, Y. Yu, D.-p. Liu, J.-m. Yan, Y. Zhang, X.-b. Zhang and Q. Jiang, Nat. Chem., 2019, 11, 64.
- 10 F. Wu, Y.-X. Yuan, X.-B. Cheng, Y. Bai, Y. Li, C. Wu and Q. Zhang, Energy Storage Materials, 2018, 15, 148.
- 11 L. Li, S. Li and Y. Lu, Chem. Commun., 2018, 54, 6648.
- 12 A. W. Abboud, E. J. Dufek and B. Liaw, J. Electrochem. Soc., 2019, 166, A667.
- 13 W. Lu, C. Xie, H. Zhang and X. Li, ChemSusChem, 2018, 11, 3996.
- 14 D. Kundu, B. D. Adams, V. Duffort, S. H. Vajargah and L. F. Nazar, Nat. Energy, 2016, 1, 16119.
- 15 H. Pan, Y. Shao, P. Yan, Y. Cheng, K. S. Han, Z. Nie, C. Wang, J. Yang, X. Li, P. Bhattacharya, K. T. Mueller and J. Liu, Nat. Energy, 2016, 1, 16039.
- 16 P. Yu, Y. Zeng, H. Zhang, M. Yu, Y. Tong and X. Lu, Small, 2019, 15, 1804760.
- 17 F. Wang, O. Borodin, T. Gao, X. Fan, W. Sun, F. Han, A. Faraone, J. A. Dura, K. Xu and C. Wang, Nat. Mater., 2018, 17, 543.
- 18 M. Chhowalla, H. S. Shin, G. Eda, L.-J. Li, K. P. Loh and H. Zhang, Nat. Chem., 2013, 5, 263.
- 19 A. K. Geim and I. V. Grigorieva, Nature, 2013, 499, 419.
- Wang, D. Xiao, M. A. Ramasubramaniam, Nat. Photonics, 2014, 8, 899.
- 21 K. Chen and L. Li, Adv. Mater., 2019, 31, 1901115.
- 22 Z. Deng, H. Jiang and C. Li, Small, 2018, 14, 1800148.
- 23 Y. Zhu, L. Peng, Z. Fang, C. Yan, X. Zhang and G. Yu, Adv. Mater., 2018, 30, 1706347.
- 24 J. Zhao, G. Zhou, K. Yan, J. Xie, Y. Li, L. Liao, Y. Jin, K. Liu, P.-C. Hsu, J. Wang, H.-M. Cheng and Y. Cui, Nat. Nanotechnol., 2017, 12, 993.
- 25 K. Raidongia and J. Huang, J. Am. Chem. Soc., 2012, 134, 16528.
- 26 A. R. Koltonow and J. Huang, Science, 2016, 351, 6280.
- 27 C. Yan, C. Lv, Y. Zhu, G. Chen, J. Sun and G. Yu, Adv. Mater., 2017, 29, 1703909.
- 28 Y. Huang, J. Liu, Q. Huang, Z. Zheng, P. Hiralal, F. Zheng, D. Ozgit, S. Su, S. Chen, P.-H. Tan, S. Zhang and H. Zhou, npj Flex. Electron., 2018, 2, 21.
- 29 Y. Omomo, T. Sasaki, J. Wang and M. Watanabe, J. Am. Chem. Soc., 2003, 125, 3568.
- 30 Z. Liu, R. Ma, Y. Ebina, K. Takada and T. Sasaki, Chem. Mater., 2007, 19, 6504.
- 31 B. Xu, S. Qi, P. He and J. Ma, Chem.-Asian J., 2019, 14, 2925.
- 32 X. Xie, M. Mao, S. Qi and J. Ma, CrystEngComm, 2019, 21,
- 33 C. Cui, H. Wang, M. Wang, X. Ou, Z. Wei, J. Ma and Y. Tang, Small, 2019, 15, 1902659.
- 34 M. Wu, W. Ni, J. Hu and J. Ma, Nano-Micro Lett., 2019, 11, 44.
- 35 W. Liu, Z. Wang, Y. Su, Q. Li, Z. Zhao and F. Geng, Adv. Energy Mater., 2017, 7, 1602834.
- 36 S. F. Li, C. Yu, J. Yang, C. T. Zhao, M. D. Zhang, H. W. Huang, Z. B. Liu, W. Guo and J. S. Qiu, Energy Environ. Sci., 2017, 10, 1958.

37 M. H. Alfaruqi, J. Gim, S. Kim, J. Song, D. T. Pham, J. Jo, Z. Xiu, V. Mathew and J. Kim, Electrochem. Commun., 2015, 60, 121.

Nanoscale Advances

- 38 Y. Yan, B. Hao, D. Wang, G. Chen, E. Markweg, A. Albrecht and P. Schaaf, J. Mater. Chem. A, 2013, 1, 14507.
- 39 D. Chao, W. Zhou, C. Ye, Q. Zhang, Y. Chen, L. Gu, K. Davey and S.-Z. Qiao, Angew. Chem., Int. Ed., 2019, 58, 7823.
- 40 S.-D. Han, S. Kim, D. Li, V. Petkov, H. D. Yoo, P. J. Phillips, H. Wang, J. J. Kim, K. L. More, B. Key, R. F. Klie, J. Cabana, V. R. Stamenkovic, T. T. Fister, N. M. Markovic, A. K. Burrell, S. Tepavcevic and J. T. Vaughey, Chem. Mater., 2017, 29, 4874.
- 41 H. Pan, Y. Shao, P. Yan, Y. Cheng, K. S. Han, Z. Nie, C. Wang, J. Yang, X. Li, P. Bhattacharya, K. T. Mueller and J. Liu, Nat. Energy, 2016, 1, 16039.
- 42 Y. Liu, Y. Zhou, J. Zhang, S. Zhang and P. Ren, J. Power Sources, 2016, 314, 1.
- 43 H. Liu, C. Li, H. P. Zhang, L. J. Fu, Y. P. Wu and H. Q. Wu, J. Power Sources, 2006, 159, 717.
- 44 R. B. Schoch, J. Han and P. Renaud, Rev. Mod. Phys., 2008, 80, 839.

- 45 D. Stein, M. Kruithof and C. Dekker, Phys. Rev. Lett., 2004, 93, 035901.
- 46 J. Lee, J. B. Ju, W. I. Cho, B. W. Cho and S. H. Oh, Electrochim. Acta, 2013, 112, 138.
- 47 G. Fang, C. Zhu, M. Chen, J. Zhou, B. Tang, X. Cao, X. Zheng, A. Pan and S. Liang, Adv. Funct. Mater., 2019, 29, 1808375.
- 48 N. Zhang, F. Cheng, J. Liu, L. Wang, X. Long, X. Liu, F. Li and J. Chen, Nat. Commun., 2017, 8, 405.
- 49 G. Dawut, Y. Lu, L. Miao and J. Chen, Inorg. Chem. Front., 2018, 5, 1391.
- 50 Q. Zhao, W. Huang, Z. Luo, L. Liu, Y. Lu, Y. Li, L. Li, J. Hu, H. Ma and J. Chen, Sci. Adv., 2018, 4, eaao1761.
- 51 P. He, M. Yan, G. Zhang, R. Sun, L. Chen, Q. An and L. Mai, Adv. Energy Mater., 2017, 7, 1601920.
- 52 L. Zhang, L. Chen, X. Zhou and Z. Liu, Adv. Energy Mater., 2015, 5, 1400930.
- 53 P. Hu, M. Yan, T. Zhu, X. Wang, X. Wei, J. Li, L. Zhou, Z. Li, L. Chen and L. Mai, ACS Appl. Mater. Interfaces, 2017, 9, 42717.