

conductivity and the adsorption rate of polysulfides, and to further alleviate the volume changes.¹⁸ The resultant composite materials usually show enhanced electrochemical performance. For example, Yu *et al.*¹⁹ reported a general method to synthesize multiscale-ordered metal-sulphide/carbon structures, which exhibit stable dis-/charge capacities for up to 300 cycles. MoS₂@C nanotubes have been produced by Qian's group²⁰ *via* the Kirkendall effect, featuring 90% capacity retention after 300 cycles at 0.5C. Lou *et al.*²¹ have synthesised uniform MoS₂ hollow spheres with a high specific capacity of 1100 mA h g⁻¹ at 500 mA g⁻¹ (~0.75C) and excellent cycling stability. Very recently, Świerczek's group has reported epitaxial growth of carbon-sheathed MoS₂ on CNTs which displays long-term stable capacities of ~900 mA h g⁻¹ at 1 A g⁻¹ (~1.5C) for 500 cycles.²²

However, most of the previously reported hierarchical structures are constructed from the nanoscale building blocks. Since electrochemical processes are electron-driven redox reactions on the atomic level, it seems extremely beneficial to optimize the design of hierarchical MoS₂ composite structures down to the single molecular layer scale. And building this highly ordered superstructure requires carefully engineering the MoS₂:C interfaces. Recent findings²³ suggest that the performance of MoS₂-based anode materials can be substantially improved by maximizing the molecular layer contact area between MoS₂ and carbon. In fact, increasing the MoS₂:C heterointerfaces has also been a guiding principle to us for developing composite MoS₂/C nanostructures. According to our previous studies, a better cycling stability and rate capability have been achieved when change from point-to-surface contacts²⁴ to a surface-to-surface architecture²⁵ (sketched in Fig. 1a and b). Rigorous advancement of this strategy to maximize the battery performance of MoS₂-based electrodes implies a layer-by-layer contact as illustrated in Fig. 1c. Such kind of molecular layer stacked structures are expected to largely enhance the multi-function of carbon species mentioned above. Moreover, the intercalation of carbon layers between the MoS₂ ones presumably provides expanded interlayer distances and hence facilitates Li⁺ diffusion so that layer-by-layer stacked composite materials exhibit extraordinarily better performance than its single components and larger scale mixtures, respectively.^{26,27} By exfoliation and reassembly, top-down methods are common ways to synthesis the layer-by-layer structures, but difficult to further build into hierarchical structures.²³ So far,

constructing this hierarchical superstructure is still challenging.

In this work, we apply a facile bottom-up method to synthesize MoS₂/N-doped carbon porous nanorods (MoS₂/NC-PNR), targeting the hierarchical superstructure to achieve high performance lithium storage. In the reported material, similar hexagonal structures enable alternating stacking of MoS₂ molecular layers and N-doped carbon layers, which promotes the largest possible contact interfaces between the active material (MoS₂ layers) and the buffer layers (carbon). In addition, such ordered stacking yields an expanded interlayer distance as compared to bulk hexagonal MoS₂ (2H-MoS₂). In this architecture, the superior properties of both MoS₂ and N-doped carbon are fully maintained while a synergetic effect due to a molecular layer level homogeneous distribution is introduced, potentially leading to ultra-fast electron and ion transfer.²⁸ Furthermore, the interoverlapped MoS₂/C nano-sheets serve as building blocks to construct a hierarchical rod-like structure which is robust enough to endure the repeated de-/lithiation processes and offers a large number of electrochemically active sites as well. These merits endow MoS₂/NC-PNR as anode material in LIB with greatly enhanced lithium storage performance. Importantly, this materials design strategy has great potential to be extended to other 2D material systems, thereby realizing high performance hierarchical materials for other energy related applications.

Results and discussion

Synthesis of the MoS₂/NC-PNR

As illustrated in Fig. 2, the MoS₂/NC-PNR superstructure was prepared *via* a modified template method. Firstly, α -MoO₃ nanorods with around several μ m long and 200 nm in diameter (see SEM images in Fig. S1a†) were mixed into a dopamine (DOPA)/TRIS solution to form a Mo(vi) – DOPA complex (MDC), which served as self-sacrifice template. The formation of this complex is indicated by the initially colourless DOPA/TRIS solution changing to a light brown suspension, immediately after the addition of the α -MoO₃ nanorods (see Fig. S1c†). During complexation of the MDC, the morphology (Fig. S1b†) and orthorhombic crystal structure (Fig. S1d†) of the α -MoO₃ nanorod template are maintained. However, the UV-vis spectra of α -MoO₃, DOPA and MDC reveal a different electronic

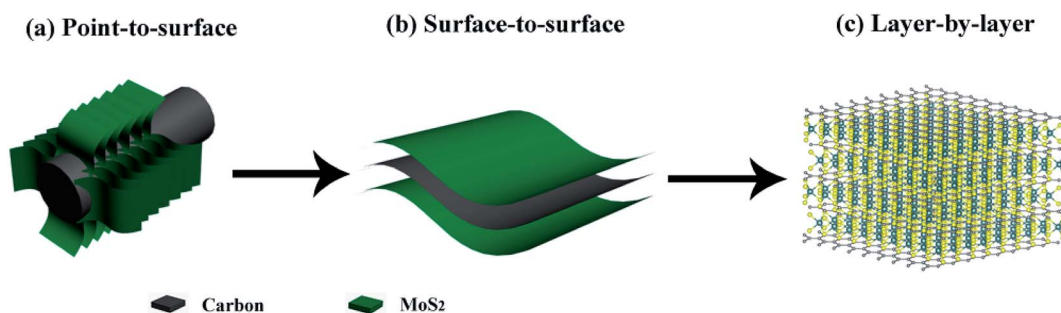


Fig. 1 Interfacial engineering of MoS₂:C: (a) point-to-surface (1D); (b) surface-to-surface (2D); (c) layer-by-layer (3D) heterointerfaces.



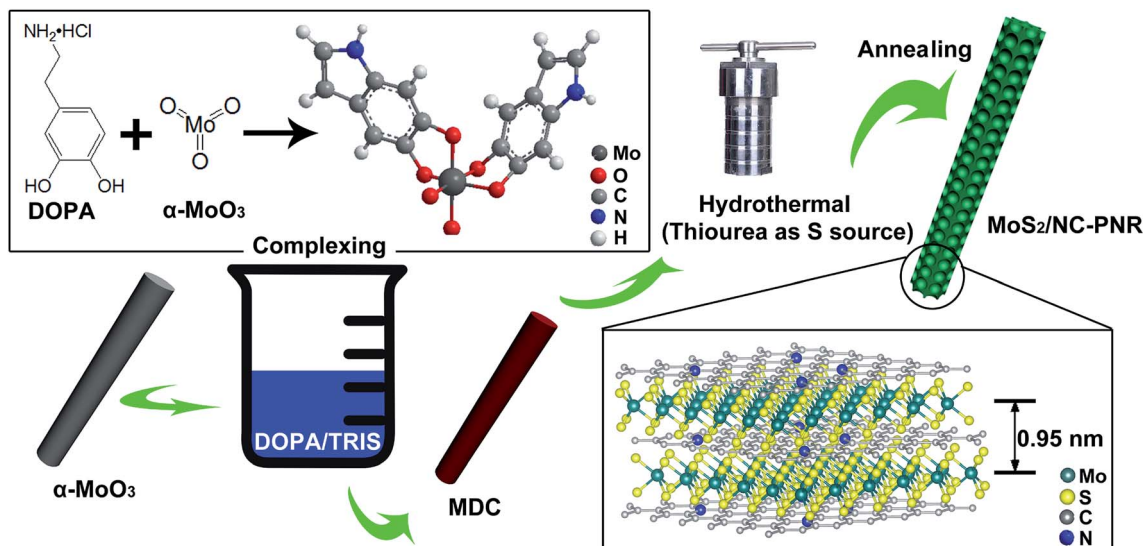


Fig. 2 Schematic illustration of $\text{MoS}_2/\text{NC-PNR}$ formation.

structure in MDC compared to $\alpha\text{-MoO}_3$ due to different chemical environments. In Fig. 3a, a broad absorption peak at about 315 nm, which corresponds to bulk-type molybdate species,^{29,30} is observed in the $\alpha\text{-MoO}_3$ spectrum but disappeared in the MDC spectrum. In the latter spectrum, an absorption peak at 280 nm presents in the same position as that of the DOPA spectrum, which originates from the $L_a\text{-}L_b$ coincident transition of DOPA molecules³¹ due to an excess amount of DOPA in the complexation suspension. High-resolution N 1s spectra of DOPA (Fig. 3b) and MDC (Fig. 3c), collected using X-ray photoemission spectroscopy (XPS), show the presence of different amines in the compounds. In case of DOPA, two species at binding energies of 401.8 eV and 399.2 eV contribute to the signal and are assigned to primary and secondary amine, respectively.³² Although the latter indicates the polymerization of DOPA to a certain degree, the main peak at 401.8 eV confirms that the dominant species is monomeric. In the N 1s spectrum of MDC, four separate peaks at 401.7 eV, 399.5 eV, 398.6 eV, and

396.5 eV are observed, which are attributed to primary, secondary and tertiary amine, and molybdenum ($\text{Mo } 3p_{3/2}$), respectively. The large share of tertiary amine, which is associated with tautomeric species of the intermediates, can be explained by electron donation from DOPA to Mo(VI) , resulting in reduced electron density in the DOPA part.³³ These results confirm the formation of the MDC complex as an essential intermediate to finally synthesize the layer-by-layer structures.

In order to obtain the final product, the MDC complex was hydrothermally treated with thiourea as the sulfur source followed by an annealing procedure. In the early stage, self-polymerization of DOPA is supposed to take place with the emission of NH_3 from thiourea which forms a mild basic environment ($\text{pH} = 10.2$ after hydrothermal reaction).³⁴ In the meantime, Mo(VI) in the MDC complex is reduced to MoS_2 with the help of H_2S , growing *in situ* on the surface of polydopamine (PDA). Thus, the hydrothermal reaction yields $\text{MoS}_2/\text{polydopamine porous nanorods}$ ($\text{MoS}_2/\text{PDA-PNR}$), which were then

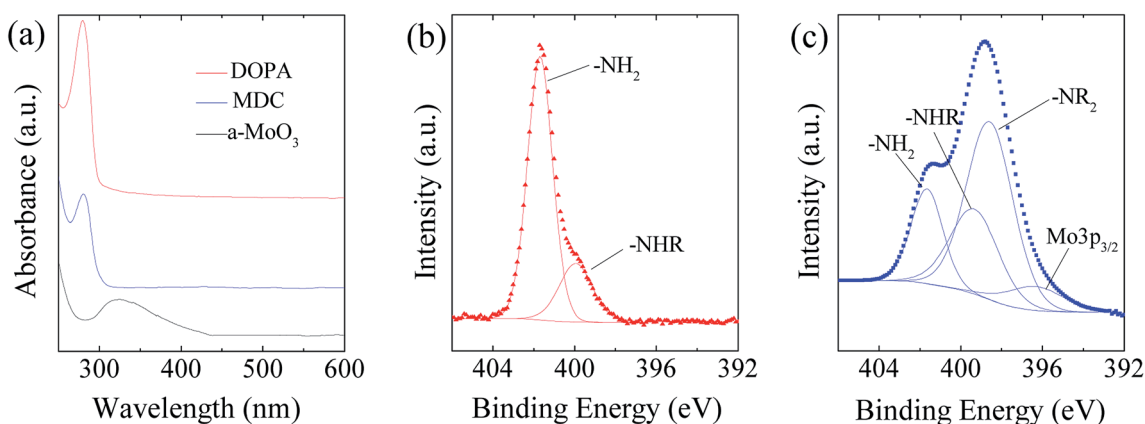


Fig. 3 (a) UV-vis spectra of $\alpha\text{-MoO}_3$, DOPA and MDC; spectra are offset for clarity. (b and c) XPS N 1s spectra of DOPA and MDC, respectively. $-\text{NH}_2$, $-\text{NHR}$ and $-\text{NR}_2$ indicate primary, secondary and tertiary amines.



sintered at 900 °C under Ar atmosphere to prepare the final product MoS₂/NC-PNR. Altogether, this procedure results in the formation of a layer-by-layer MoS₂/NC structure while on the larger length scale the porous nanorod morphology is maintained.

Characterization of the interoverlapped structure

Analysis of the chemical composition of the resultant MoS₂/NC-PNR superstructure was carried out by means of XPS, displayed in Fig. 4a and S2†. The survey spectrum (Fig. S2a†) shows distinct peaks of Mo, S, C, N and O in which the molar ratio of S : Mo equals 2.40 ± 0.01. The discrepancy to the stoichiometry of MoS₂ can be explained by surface defects of the nanocomposite.³⁵ A high-resolution scan of the Mo 3d range (Fig. 4a left) shows a doublet at 229.2 eV and 232.7 eV, which is attributed to the Mo⁴⁺ in MoS₂. A minor contribution from MoO_x is also observed. The S 2p spectrum (Fig. S2b†) consists of a single doublet at binding energies of 162.3 eV and 163.6 eV, which relates to the S 2p_{3/2} and 2p_{1/2} orbitals of S²⁻.³⁶ In the C 1s spectrum (Fig. 4a mid), a dominant C=C signal at 284.5 eV and traces of a C=O one at 287.4 eV are observed, indicating low oxygen content in the carbon layers. Furthermore, the C-N species at 285.8 eV accounts for 14.1% of all carbon, revealing the N-rich nature of the carbon component.³⁷ The N 1s

spectrum (Fig. 4a right) is composed of a Mo 2p_{3/2} peak and three different N species, *i.e.*, graphitic, pyrrolic, and pyridinic, suggesting a successful doping of N into the carbon layer.³⁸ The Raman shift spectrum of MoS₂/NC-PNR in Fig. 4b further confirms the chemical composition of the hierarchical superstructure. At lower wave numbers, the peaks present at 383.43 and 404.71 cm⁻¹ correspond to the in-plane E_{2g}¹ and out of plane A_{1g} mode of MoS₂, respectively.³⁹ It is worth noting that the A_{1g} peak is more pronounced than the E_{2g}¹ peak, indicating a more edge-terminated and less layered structure.⁴⁰ Actually, the frequency difference of the two peaks $\Delta k = 21.28 \text{ cm}^{-1}$ is close to the value of single layer MoS₂ reported in the literature³⁹ (20.2–21.2 cm⁻¹), suggesting that single layer MoS₂ is featured in the MoS₂/NC-PNR composite. At higher wave numbers, characteristic peaks at 1369 and 1598 cm⁻¹ correspond to disordered carbon (D-band) and ordered graphitic carbon (G-band), respectively, with a peak intensity ratio of approximately 1 : 1. The pronounced D-band indicates a defect rich nature of the N-doped carbon layers.

The TGA data (Fig. 4d) of both MoS₂/NC-PNR and bulk MoS₂ illustrate oxidation of MoS₂ to MoO₃, accompanied by a theoretical mass loss of 10.1 wt%. The bigger total mass loss in case of MoS₂/NC-PNR confirms a significant carbon content, which is determined to 25.8 wt%, assuming complete C combustion.

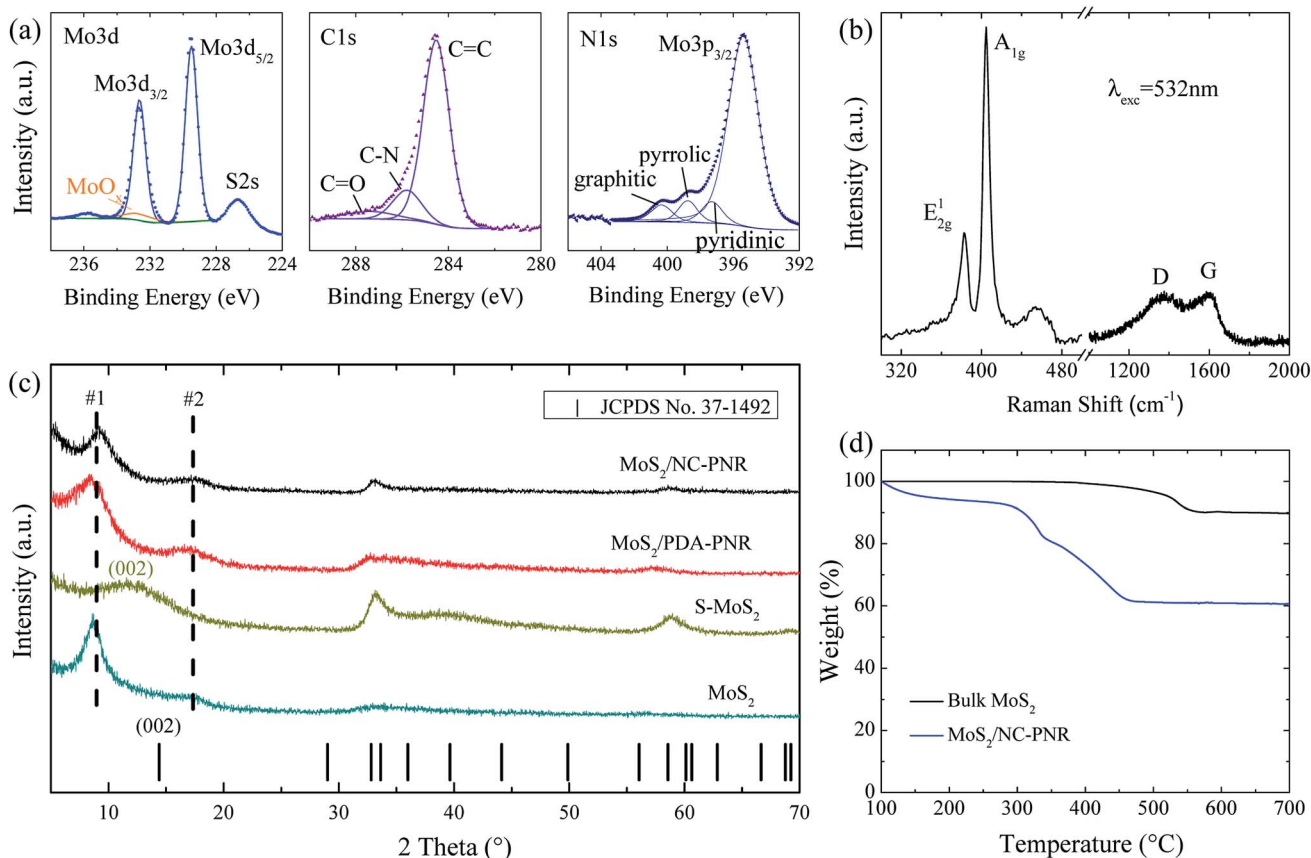


Fig. 4 (a) XPS Mo 3d, C 1s and N 1s spectrum of MoS₂/NC-PNR; (b) Raman spectrum of the MoS₂/NC-PNR excited at 532 nm; (c) XRD patterns of MoS₂/NC-PNR, MoS₂/PDA-PNR, S-MoS₂ and MoS₂. Vertical ticks display the standard Bragg peaks of MoS₂ (JCPDS no. 37-1492); (d) TGA curve of MoS₂/NC-PNR and of bulk MoS₂.



In addition, the onset of oxidation at lower temperatures compared to bulk MoS₂ further indicates the defect rich nature of the MoS₂/NC-PNR superstructure. XRD patterns of both MoS₂/PDA-PNR and MoS₂/NC-PNR as well as of pure MoS₂ samples are displayed in Fig. 4c. Instead of one Bragg peak below 20° in case of standard 2H-MoS₂ (JCPDS no. 37-1492), two new broad peaks appear, corresponding to *d* spacings of 9.7 Å (#1) and 5.1 Å (#2), respectively, for both MoS₂/PDA-PNR and MoS₂/NC-PNR. Taking the interlayer distances of standard MoS₂ (6.2 Å) and graphitic carbon (3.4 Å)^{23,40} into account, the combined “crystallographic layer thickness” is expected to be 9.6 Å, which agrees with the *d* spacing of 9.7 Å (#1) determined from XRD. Therefore, the more pronounced peak #1 at 9.1° can be assigned to the (002) reflection of MoS₂, whose interlayer distance is enlarged by the interoverlapped N-doped carbon layers, while the peak at 17.4° (#2) might belong to a higher order diffraction along the *c*-direction. Few recent works^{41–43} also reported hydrothermally synthesized MoS₂ nanostructures with an expanded interlayer distance of 9.5 Å, which was ascribed to either amine insertion between the MoS₂ layers or oxygen incorporation under hydrothermal conditions. However, these structures are only stable below 260 °C. At high temperatures, the expanded structure will shrink. In contrast, the MoS₂/PDA-PNR is thermodynamically stable as the interlayer expansion is maintained upon sintering at 900 °C (MoS₂/NC-PNR), as evidenced by very similar XRD patterns in Fig. 4c. But this is not the case for the pure MoS₂ sample, where dopamine was not added to the reaction solution, which hence does not show the characteristic Bragg peak #1 anymore after sintering (S-MoS₂, Fig. 4c). In addition, with the large interlayer distance and the N-doped carbon layers in between, the MoS₂ layers are expected to exhibit monolayer behavior, which is revealed by the Raman spectra. In summary, a MoS₂/NC-PNR superstructure was confirmed by both crystallographic and spectroscopic methods. Additional morphological analysis also supports this conclusion, which will be discussed in detail in the following part. The resulting superstructure offers a novel way of assembling materials in a chosen sequence by precise arrangement of the building blocks within molecular layer scale.⁴² Owing to the similar hexagonal layered structure of the single components MoS₂ and carbon, even weak van der Waals forces are sufficient to stabilize the stacked structure, which maximizes the molecular contact area and consequently the synergetic effects.²³

Characterization of the hierarchical structure

From the structural point of view, MoS₂/NC-PNR is more advanced than a simple interoverlapped structure because it exhibits an additional hierarchical arrangement. The structural organisation of MoS₂/NC-PNR at different length scales is presented in Fig. 5, including a schematic summary in Fig. 5g. By virtue of the α-MoO₃ template, MoS₂/NC-PNR features a rod-like morphology on the micrometer scale. The SEM/TEM images in Fig. 5a and b show that the rods are still several μm long, but increased in diameter from 200 nm to around 600 nm. The magnified images in Fig. 5c and d reveal that the rods are constructed by homogeneous nanosheets of around 20 nm

thick. The MoS₂/NC nanosheets crosslink to form a 3D porous structure with a pore size of 100–200 nm, resulting in a high specific surface area of 26.9 ± 0.7 m² g⁻¹ as compared to 6.97 ± 0.03 m² g⁻¹ of the pure S-MoS₂ nanosheet agglomerates (see Fig. S3†). HR-TEM tilt-series were recorded and reconstructed to further confirm the nanosheets constructed rod-like structure. In a tilt-series movie (Movie S1†), one can clearly see that the lines of the stacking appear and disappear depending on how the sample is oriented. This is highlighted in Fig. 6 which shows selected frames from the movie. The red and white arrows indicate the same parts of the nanorod as it is being tilted. The red arrow points to an area, which shows the lines of the stacking for the negative tilt-angles. While for the sample tilted in such a manner at 35° and 61°, no stacking lines were observed, indicating that the projection goes straight through the layers. The tilt-series shows that the nanorod indeed consists of the proposed nanosheets building blocks (Fig. 5). By tilting the sample, the largest interlayer distance of the red arrow marked area, which corresponds to the actual interlayer distance of the MoS₂/NC-PNR, was determined. The corresponding HR-TEM image (Fig. 5e) suggests that the MoS₂/NC nanosheets consist of smaller subunits. The lattice fringes exhibit an ordered layer structure with 3–5 layers. Fig. 5f presents the line scan of the white arrow in Fig. 5e, from which the interlayer distance is determined to be 0.96 ± 0.16 nm. This value is in accordance with the *d* spacing value of the XRD peak #1 (Fig. 4c), confirming the alternately stacked superstructure. It is worth noting that the hierarchical porous nanorod structure cannot be realized without the addition of DOPA during the synthesis. Abundant N-doped carbon introduced by the carbonized self-polymerized DOPA acts as additional backbone for the superstructure, as evidenced by the non-layered parts in the HR-/TEM images in Fig. 5. On the contrary, S-MoS₂ synthesized by the same procedure but without adding DOPA does not maintain the nanorod morphology during hydrothermal treatment, but forms blossom-like agglomerates of MoS₂ nanosheets (see Fig. S4†).

High-performance lithium storage

The structural advance endows the MoS₂/NC-PNR with excellent lithium storage performance, which was studied by cyclic voltammetry (CV) and galvanostatic cycling in the voltage range of 0.01–3.0 V vs. Li/Li⁺. The CV curves of MoS₂/NC-PNR at 0.1 mV s⁻¹ are presented in Fig. 7a. Two pronounced reduction peaks at 1.01 V and 0.65 V during the initial cathodic scan are typical features of MoS₂-based electrode materials, corresponding to the Li⁺ intercalation into MoS₂ interlayer space and the subsequent conversion reaction of Li_xMoS₂ to metallic Mo and Li₂S, respectively.^{43,44} Due to the irreversible nature of the conversion reaction, both peaks vanish during the following cycles while a broad reduction peak appears around 1.92 V from the 2nd cycle on, which corresponds to the stepwise reduction of S to S²⁻.²⁴ It belongs to the reversible redox pair Li₂S/S with the related oxidation peak at 2.25 V in the first anodic scan, where Li₂S is oxidized to elemental S.⁴⁵ The Li₂S/S redox pair shows very good cycling stability, except a slight decrease in intensity



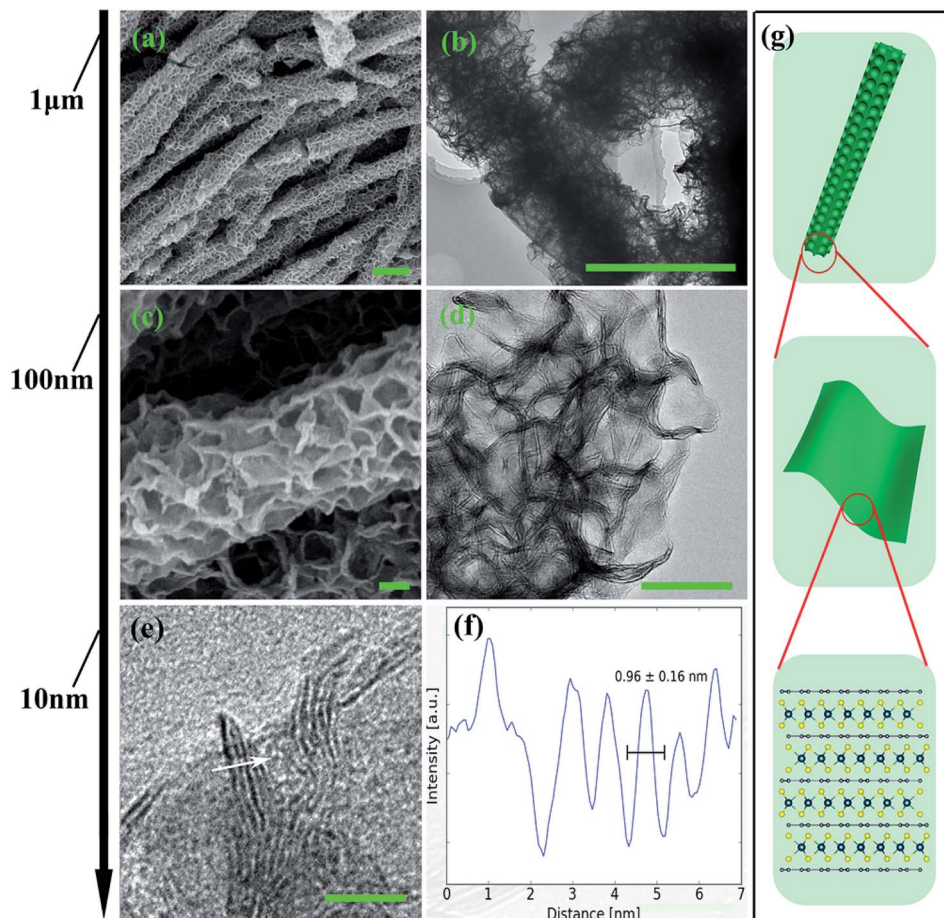


Fig. 5 Structural organisation of MoS₂/NC-PNR on several length scales: (a, c) SEM images (scale bar 1 μm), (b, d) TEM images (scale bar 100 nm), (e) HR-TEM images (scale bar 10 nm), (f) line scan of the white arrow in (e) and (g) schematic illustration of the hierarchical structure.

and a moderate shift of the oxidation peak up to 2.31 V in cycle 10. Upon continued cycling, further electrochemical activity is identified by means of several reductive and oxidative features in the voltage ranges of 0.2–1.6 V (cathodic) and 1.1–1.9 V (anodic). They may, *i.e.*, originate from the de-/lithiation of an amorphous Mo/Li₂S matrix, including the re-formation of MoS_x. The N-doped carbon in the superstructure can also accommodate Li⁺, which is indicated by a distinct stable reduction feature at 0.01 V.

The charge–discharge profile of a MoS₂/NC-PNR-based electrode upon galvanostatic cycling at a current density of 0.5C (1C = 670 mA g⁻¹) is shown in Fig. 7b. In agreement with the CV curves, there are two plateaus at ~1.0 and ~0.7 V during the first discharge process referring to the different lithium storage processes, while only one prominent plateau appears at ~2.2 V during the first charge process. From the second cycle on, the dominant plateaus at 2.0/2.25 V as well as the slopes below 2.0 V, corresponding to the Li₂S/S redox pair, show quite reversible behavior, which is superior to usually reported Li–S batteries.⁴⁶ The observed high reversibility may be promoted by the N-doped carbon layers and by the appearance of conductive Mo nanoparticles.¹² The stacked N-doped carbon layers could offer physical confinement to the active species and provide

more electroactive sites for the strong chemisorption of lithium polysulfides. The Mo nanoparticles derived from the MoS₂ reduction boost the electrochemical reaction, further hindering the polysulfide shuttle effect. As a result, the corresponding cycling performance in Fig. 7c presents a stable discharge capacity of ~800 mA h g⁻¹ for up to 150 cycles after initial decay from 1086 mA h g⁻¹. The initial capacity loss is mainly attributed to the partially irreversible conversion reaction and the formation of solid-electrolyte interphase (SEI).⁴⁷ The durable cycling capability of the hierarchical superstructure is highlighted by the comparison with a S-MoS₂ electrode, whose discharge capacities drop noticeably after 40 cycles before stabilizing at around underwhelming 30 mA h g⁻¹. The poor cycling stability of S-MoS₂ can be attributed to structural changes of the active MoS₂ material as well as the shuttle effect of *in situ* formed (poly)sulfide from the 2nd cycle on.⁴⁸ However, the MoS₂/NC-PNR superstructure design specifically aims at maintaining the high specific capacities by maximizing the interfacial contact area between active material and interoverlapped carbon, which may buffer the mechanical strain to the largest extend possible.²³ In the SEM images of electrodes after 150 cycles (Fig. S5†), the rod-like morphology of MoS₂/NC-PNR is partially preserved, while in case of the S-MoS₂ material only



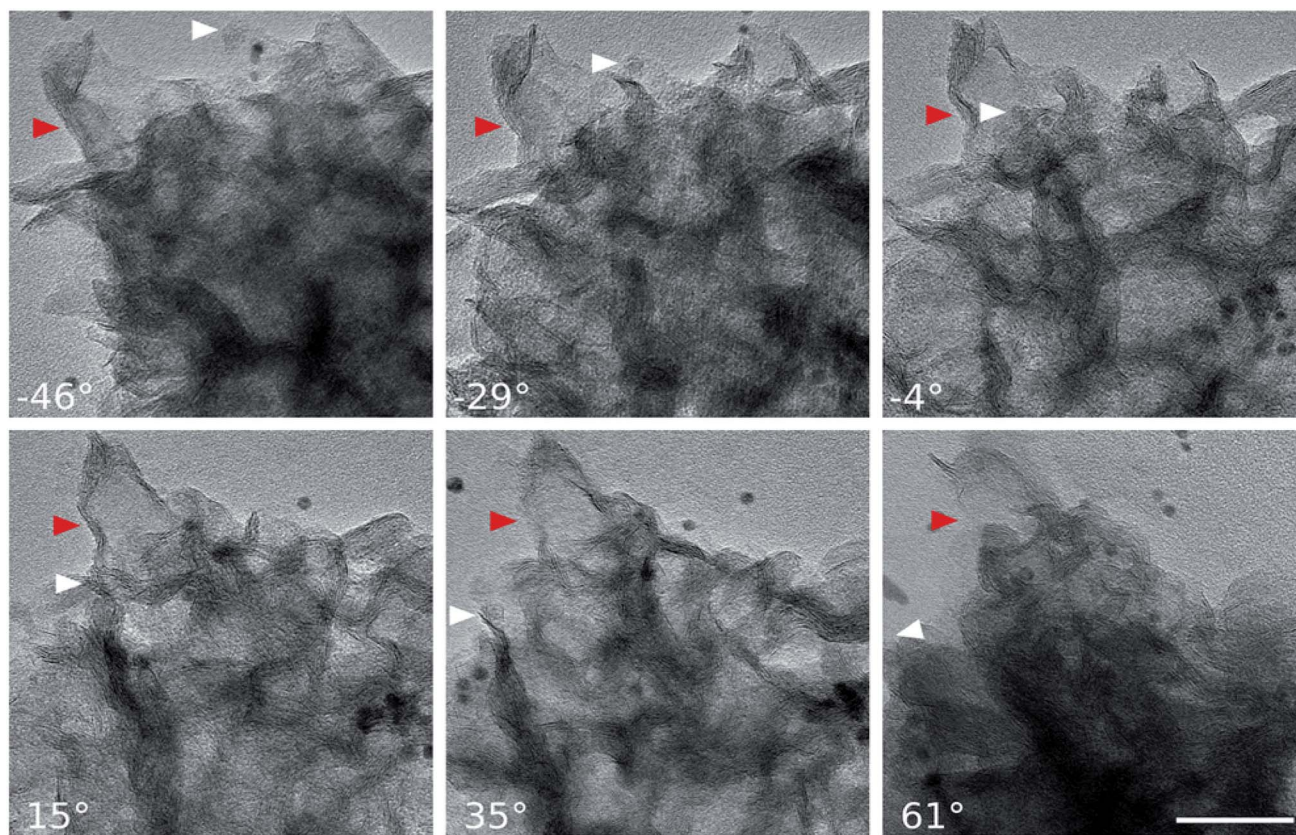


Fig. 6 HR-TEM images: selected frames from a movie (Movie S1†) showing a tilt series. The arrows indicate the same part of the nanorod as it is being tilted. While -46° to 15° show the lines of the stacking, indicated by the red arrow, the sample is tilted in such a manner at 35° and 61° , that the projection goes straight through the layers (scale bar: 50 nm).

irregular nanoparticles remained. Further post mortem characterizations of the MoS₂/NC-PNR electrode demonstrate the buffer function of the N-doped carbon layers to the amorphous products. In Fig. S6a,† the XRD patterns of the MoS₂/NC-PNR electrode after cycling suggest completely non-crystallized feature of the MoS₂ structure. The HAADF-STEM image of the cycled electrode and the corresponding SAED patterns in Fig. S7a–c† also present a disordered structure of the Mo species. In the SAED patterns, the only weak diffraction rings can be indexed as disordered graphitic carbon. The EDX together with the STEM images (Fig. S7d–f†) indicate a homogeneous Mo distribution in the carbon matrix. All the results highlight the significant role of carbon in maintaining the structural integrity of the electrode. Therefore, the MoS₂/NC-PNR electrode exhibits an ultra-long cycling lifetime of 700 cycles at a current of 2C, delivering a stable capacity of $\sim 520 \text{ mA h g}^{-1}$ as shown in Fig. 7e. In addition, the N-doped carbon layers compensate the intrinsic low conductivity of MoS₂ in MoS₂/NC-PNR, allowing faster electron transfer during the dis-/charge process.⁴⁹ As a consequence, the MoS₂/NC-PNR electrode shows much improved rate capability as compared to the S-MoS₂ electrode (Fig. 7d). The former exhibits an initial discharge capacity of 1294 mA h g^{-1} at 0.1C, stabilizing at 810, 720, 636, 575, and 507 mA h g^{-1} upon increasing the current density to 0.2, 0.5, 1, 2, and 5C, respectively. All of the values are

higher than that of the latter. Especially at high current density of 10C, the MoS₂/NC-PNR electrode presents a large reversible capacity of 443 mA h g^{-1} , which is twice the value of the S-MoS₂ electrode.

In order to clarify the enhanced electrochemical kinetics of the MoS₂/NC-PNR electrode, further CV measurements and electrochemical impedance spectroscopy (EIS) have been carried out. The CV curves at different scan rates (see Fig. 8a,) show similar shape, which indicates excellent adaptability even at large scan rates. The peak current (I) and the scan rate (ν) obey a power law $I = a\nu^b$, from which both the capacitive and the diffusion controlled contributions of the charge storage process can be evaluated.⁵⁰ Fitting the data in Fig. 8b yields that the parameter b equals to 1.02, 0.86, 0.77 and 0.88 for the cathodic and anodic peaks (C1, C2, A1, A2), respectively. The values suggest that capacitive processes (mainly the redox pseudocapacitive contribution) are dominant in the associated electrochemical reactions. The exact (pseudo)capacitive and diffusion controlled contributions can be assessed by using the equation $I = k_1\nu + k_2\nu^{1/2}$ (see Fig. S8†).⁵¹ In Fig. 8c, the (pseudo)capacitive contribution is proportional to the scan rate, reaching 85% at 2 mV s^{-1} . The high (pseudo)capacitive contribution suggests fast redox reactions in the MoS₂/NC-PNR electrode, which is straightforwardly attributed to the effective contact between MoS₂ and N-doped carbon as well as the porous nanorods



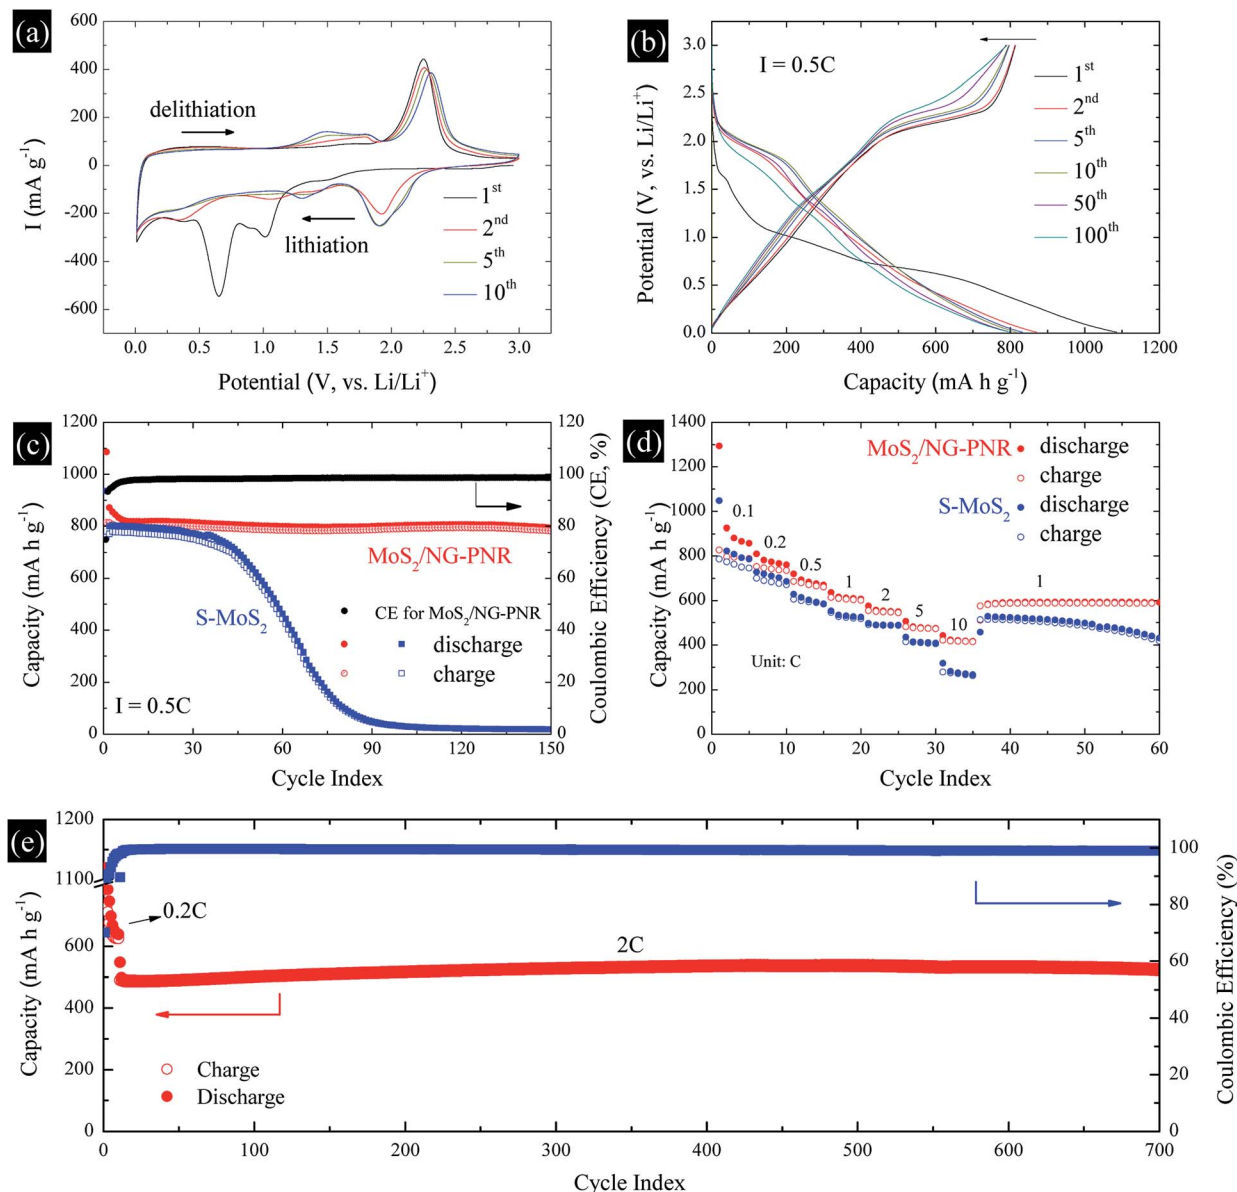


Fig. 7 Electrochemical performance of $\text{MoS}_2/\text{NC-PNR}$: (a) CV, (b) GCDL measurements at specific cycles, (c) cycling stability at 0.5C and the comparison with S-MoS_2 , (d) rate capability and (e) long-term cycling stability at 2C (activated at 0.2C for 10 cycles).

architecture. This conclusion is further supported by EIS. In the Nyquist plots obtained at open circuit voltage (OCV) in Fig. 8d, both $\text{MoS}_2/\text{NC-PNR}$ - and S-MoS_2 -based electrodes show a depressed semi-circle in the high to medium frequency range as well as a sloping behavior in the low frequency range. The diameter of the semicircle, which correlates with the charge transfer resistance (R_2 in the corresponding equivalent circuit as shown in the inset of Fig. 8d), is only half the value in $\text{MoS}_2/\text{NC-PNR}$ ($183 \pm 2 \Omega$) compared to S-MoS_2 ($342 \pm 1 \Omega$). Upon cycling, R_2 decreases abruptly in the $\text{MoS}_2/\text{NC-PNR}$ electrode (Fig. S9†) which can be attributed to irreversible structural changes during the initial lithiation. Interestingly, the $\text{MoS}_2/\text{NC-PNR}$ electrode exhibits few changes in subsequent cycles, which also holds for the low frequency domain, revealing a stable and reversible de-/lithiation process. These results

imply not only improved conductivity of the pristine $\text{MoS}_2/\text{NC-PNR}$ compound, but also more efficient ion transport pathways through the N-doped carbon layers of the superstructure.

The abovementioned results clearly imply that the hierarchical MoS_2/C composite with well-designed molecular contact interface ensures an enhanced electrochemical performance. This conclusion is further confirmed by comparing the present results with our previous work.²⁵ In ref. 27, we have reported $\text{C@MoS}_2@\text{C}$ sandwiched hollow spheres with a surface-to-surface contact between MoS_2 and carbon layers. Interestingly, the carbon content in $\text{C@MoS}_2@\text{C}$ sandwiched hollow spheres and the $\text{MoS}_2/\text{NC-PNR}$ superstructures is almost identical ($\sim 26\%$). With the same chemical composition, the major differences between the two materials are the interfacial contact and morphological architecture. Due to its much more effective



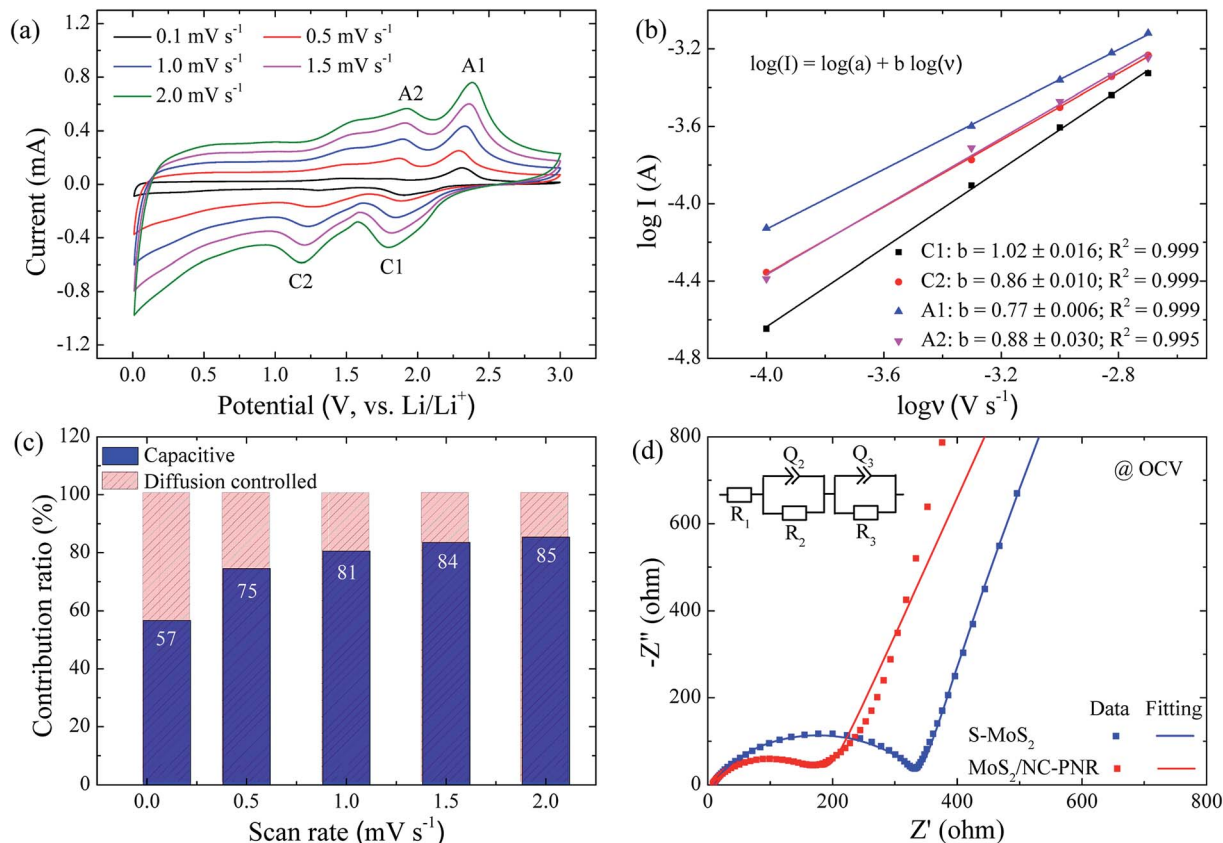


Fig. 8 Kinetic analysis of MoS₂/NC-PNR as LIB anode: (a) CV curves at different scan rate; (b) current response versus scan rate ($\log I$ vs. $\log v$) plots at each redox peak; (c) capacitive and diffusion controlled contributions to the electrochemical processes at corresponding scan rate; the number labels the percentile capacitive contributions; (d) Nyquist plots and the fitting curves of MoS₂/NC-PNR and S-MoS₂ electrodes. The inset shows the equivalent circuit.

interfacial contact (layer-by-layer contact), the MoS₂/NC-PNR electrode exhibits well enhanced electrochemical performance as compared to the C@MoS₂@C electrode including higher capacities of ~ 800 mA h g⁻¹ vs. ~ 640 mA h g⁻¹ at 0.5C; longer cycling stability up to 700 cycles at 2C vs. 200 cycles at 1C; and a better rate capability of 507 mA h g⁻¹ vs. 382 mA h g⁻¹ at 5C. Actually, these values are comparable or even better than most of recently published MoS₂-based hierarchical structures as seen in Table S1† while our approach employs an advantageous environmentally friendly synthetic route and exploits a low cost, easy access carbon source. In general, the reported performances show that the rational structure design of nanocomposites is indispensable to their application potential and the present work provides a route to realize such a hierarchical structure down to the molecular layer level.

Conclusions

In summary, we report on a hierarchically structured nanocomposite with optimized atomic interfacial contact for application in lithium ion batteries. The MoS₂/NC-PNR superstructure has been prepared by means of a one-pot synthesis approach. The alternating stacking of the MoS₂ layers with intercalated N-doped carbon layers provides

a maximum specific contact area between the active material and the buffer layers, effectively alleviating the loss of active material due to pulverization of MoS₂ or dissolution of polysulfides. In addition, the buffer layers also act as a conductive matrix, enabling faster Li-ion and electron transfer during the de-/lithiation processes. At a larger length scale, the rod-like porous structure offers large specific surface area and abundant active sites for electrochemical reactions which also contributes to the dominant capacitive charge storage behaviour. As a result, the interfacially engineered MoS₂/NC-PNR superstructure exhibits a high specific capacity of 1294 mA h g⁻¹ at 0.1C, stable cycling performance up to 700 cycles at 2C, and a high rate capability of 443 mA h g⁻¹ at 10C. The ordered MoS₂/NC-PNR superstructure with well-defined interfaces is capable of buffering huge mechanical strain and offering efficient electron and ion transport pathways, which indicates a new way of rationally designing other hierarchical functional materials.

Experimental methods

Synthesis of α -MoO₃ nanorods

α -MoO₃ nanorods were prepared through a hydrothermal method according to the literature.⁵² 1000 mg ammonium



molybdate tetrahydrate (AMT, Sigma-Aldrich, 81.0–83.0% MoO₃ basis) was dissolved in 34 mL deionized water. 6 mL nitric acid (65 wt%) was added dropwise before stirring the AMT solution for 15 min. After stirring for another 15 min, the mixture was transferred to a 50 mL Teflon autoclave, heating at 180 °C for 24 h. The milky white precipitate was washed and collected for further use.

Synthesis of MoS₂/NC-PNR superstructure and S-MoS₂

MoS₂/NC-PNR was produced by adding α -MoO₃ nanorods into a dopamine/Tris solution and then stirring for 24 h. Then the precipitate was centrifuged and added into a thiourea solution under vigorous stirring. The homogeneously dispersed suspension was hydrothermally treated at 200 °C for 24 h. After the reaction, the black precipitate was washed with distilled water and ethanol for at least 3 times before vacuum drying at 80 °C. Finally, the black powder was sintered at 900 °C for 3 h under Ar atmosphere. For comparison, pure MoS₂ nanosheets were synthesized by using the same α -MoO₃ nanorods and same sulfur source at the same hydrothermal conditions and subsequent thermal treatment. The pure MoS₂ samples before and after sintering are labeled as MoS₂ and S-MoS₂, respectively.

Characterization

The morphology and microstructure of the sample was characterized by scanning electron microscopy (SEM, ZEISS Leo 1530) and transmission electron microscopy (TEM, JEM 2100F). TEM tilt-series images were acquired using a ZEISS Libra 200 MC Cs-Corr DMU Kronos with 200 kV acceleration voltage at highest magnification (pixel size: 0.578 Å) from –68° to +64° in 1° steps. 5 images were acquired at each step with exposure times of 1000 ms, which were later aligned and summed to increase resolution. The tilt-series was then aligned using the software provided by the IMOD package.^{53–55} For TEM measurement, the sample (powder) was dispersed in ethanol : water (2 : 1) mixture at 3 mg mL⁻¹. The dispersion was ultrasonicated for 30 minutes and then centrifuged at 14 800 rpm for 60 seconds. 1 μ L of the material that had collected at the bottom of the tube was then mixed with 30 μ L of water. 2.5 μ L of this mixture was dropped onto a copper TEM grid with carbon-coated Formvar film. Before the sample could dry, 2.5 μ L of a mixture of water and gold fiducials (6 nm in size), used for image alignment, was dropped onto both sides of the TEM grid. After waiting for one minute, excess liquid was carefully removed with filter paper.

X-Ray powder diffraction (XRD) was performed in Bragg–Brentano geometry (Bruker-AXS D8 ADVANCE ECO) applying Cu-K _{α} 1 radiation ($\lambda = 1.54056$ Å). The step size $\Delta 2\theta$ was 0.02° with a scan speed of 0.5° min⁻¹. X-ray photoemission spectroscopy (XPS) was carried out in an ESCALAB 250Xi ultra-high vacuum system with an Al K _{α} radiation source ($h\nu = 1486.6$ eV), 900 μ m spot size and 20 eV pass energy. Nitrogen physisorption measurements were performed at 77 K with a Gemini V (Micromeritics, Norcross, GA) after degassing the sample at 120 °C for 2 h. Brunauer–Emmett–Teller (BET) analysis from the amount of N₂ absorbed at various relative vapor pressures (six points

0.05 < P/P_0 < 0.3, nitrogen molecular cross-sectional area = 0.162 nm²) was used to determine the surface area. Barrett–Joyner–Halenda (BJH) analysis was done on the adsorption isotherms in order to obtain the pore-size distribution. Raman spectroscopy was performed on bulk powder samples using a Renishaw InVia microscope with 532 nm excitation lasers in air under ambient conditions. The laser power was kept below 100 μ W to avoid decomposition. Measurements on minimum five different spots were performed and showed the samples to be highly homogeneous under these measurement conditions. The spectra were baseline corrected and averaged after acquisition. UV-vis absorption spectra were measured with a Jasco UV-660 spectrophotometer in the range from 250 to 600 nm. The absorption of the substrate was subtracted as baseline correction. Thermogravimetric analysis was performed by using a TGA/DSC1 STARE System (Mettler Toledo) at a heating rate of 10 °C min⁻¹ in air.

Electrochemical measurement

Electrochemical studies were carried out using Swagelok-type cells.⁵⁶ For both the pure MoS₂ and the MoS₂/NC-PNR electrodes, the active material, carbon black (SuperP, Timcal) and polyvinylidene fluoride (PVDF, Sigma-Aldrich, 99%) binder were mixed in anhydrous 1-methyl-2-pyrrolidinone (NMP, Sigma-Aldrich, 99%) with a weight ratio of 7 : 2 : 1. The slurry was pasted on a circular Cu plate (~10 mm in diameter) with a mass loading of 1 mg cm⁻², dried overnight under vacuum at 80 °C and pressed. The two-electrode Swagelok-type cells were assembled in an Ar atmosphere glove box using lithium foil as counter electrode and 1 M LiPF₆ in a 1 : 1 mixture of ethylene carbonate and dimethyl carbonate as liquid electrolyte (Merck LP30). Cyclic voltammetry and galvanostatic cycling of the cells were performed at 25 °C between 0.01 and 3.0 V *versus* Li/Li⁺ at various scan/current rates using a VMP3 multichannel potentiostat (Bio-Logic SAS). Electrochemical impedance spectroscopy (EIS) was carried out also by using the VMP3 multichannel potentiostat in the frequency range of 100 kHz to 0.1 Hz. The EIS data were analyzed with the help of the Z Fit function of the EC-Lab software (Bio-Logic).

Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors thank I. Glass for experimental support. Financial support by the CleanTech-Initiative of the Baden-Württemberg-Stiftung (Project CT3 Nanostorage) and by the IMPRS-QD is gratefully acknowledged. Z. L. acknowledges financial support



by the Chinese Scholarship Council, the Excellence Initiative of the German Federal Government, and by the Götze foundation.

References

- 1 Y. J. Tang, Y. Wang, X. L. Wang, S. L. Li, W. Huang, L. Z. Dong, C. H. Liu, Y. F. Li and Y. Q. Lan, *Adv. Energy Mater.*, 2016, **6**, 1600116.
- 2 L. Yu, B. Y. Xia, X. Wang and X. W. Lou, *Adv. Mater.*, 2016, **28**, 92–97.
- 3 M.-L. Tsai, S.-H. Su, J.-K. Chang, D.-S. Tsai, C.-H. Chen, C.-I. Wu, L.-J. Li, L.-J. Chen and J.-H. He, *ACS Nano*, 2014, **8**, 8317–8322.
- 4 X. Gu, W. Cui, H. Li, Z. Wu, Z. Zeng, S.-T. Lee, H. Zhang and B. Sun, *Adv. Energy Mater.*, 2013, **3**, 1262–1268.
- 5 P. T. Dirlam, J. Park, A. G. Simmonds, K. Domanik, C. B. Arrington, J. L. Schaefer, V. P. Oleshko, T. S. Kleine, K. Char, R. S. Glass, C. L. Soles, C. Kim, N. Pinna, Y.-E. Sung and J. Pyun, *ACS Appl. Mater. Interfaces*, 2016, **8**, 13437–13448.
- 6 S. H. Choi, Y. N. Ko, J.-K. Lee and Y. C. Kang, *Adv. Funct. Mater.*, 2015, **25**, 1780–1788.
- 7 C. Zhu, X. Mu, P. A. van Aken, Y. Yu and J. Maier, *Angew. Chem., Int. Ed.*, 2014, **53**, 2152–2156.
- 8 X. Chen, *Small Methods*, 2017, **1**, 1600029.
- 9 M.-R. Gao, Y.-F. Xu, J. Jiang and S.-H. Yu, *Chem. Soc. Rev.*, 2013, **42**, 2986–3017.
- 10 Z. Hu, Q. N. Liu, W. Y. Sun, W. J. Li, Z. L. Tao, S. L. Chou, J. Chen and S. X. Dou, *Inorg. Chem. Front.*, 2016, **3**, 532–535.
- 11 T. Stephenson, Z. Li, B. Olsen and D. Mitlin, *Energy Environ. Sci.*, 2014, **7**, 209–231.
- 12 X. Fang, X. Guo, Y. Mao, C. Hua, L. Shen, Y. Hu, Z. Wang, F. Wu and L. Chen, *Chem.–Asian J.*, 2012, **7**, 1013–1017.
- 13 Y. M. Chen, X. Y. Yu, Z. Li, U. Paik and X. W. Lou, *Sci. Adv.*, 2016, **2**, e1600021.
- 14 L. Zhang, H. B. Wu, Y. Yan, X. Wang and X. W. Lou, *Energy Environ. Sci.*, 2014, **7**, 3302–3306.
- 15 F. Gong, L. Peng, H. Liu, Y. Zhang, D. Jia, S. Fang, F. Li and D. Li, *J. Mater. Chem. A*, 2018, **6**, 18498–18507.
- 16 W. Wang, P. Yang, Z. Jian, H. Li, Y. Xing and S. Zhang, *J. Mater. Chem. A*, 2018, **6**, 13797–13805.
- 17 N. Liu, Z. Lu, J. Zhao, M. T. McDowell, H.-W. Lee, W. Zhao and Y. Cui, *Nat. Nanotechnol.*, 2014, **9**, 187–192.
- 18 P.-p. Wang, H. Sun, Y. Ji, W. Li and X. Wang, *Adv. Mater.*, 2014, **26**, 964–969.
- 19 C. Wu, J. Maier and Y. Yu, *Adv. Mater.*, 2016, **28**, 174–180.
- 20 X. Zhang, X. Li, J. Liang, Y. Zhu and Y. Qian, *Small*, 2016, **12**, 2484–2491.
- 21 Y. Wang, L. Yu and X. W. Lou, *Angew. Chem., Int. Ed.*, 2016, **55**, 7423–7426.
- 22 Z. Zhang, H. Zhao, Y. Teng, X. Chang, Q. Xia, Z. Li, J. Fang, Z. Du and K. Świerczek, *Adv. Energy Mater.*, 2018, **8**, 1700174.
- 23 H. Jiang, D. Ren, H. Wang, Y. Hu, S. Guo, H. Yuan, P. Hu, L. Zhang and C. Li, *Adv. Mater.*, 2015, **27**, 3582.
- 24 Z. Li, A. Ottmann, E. Thauer, C. Neef, H. Sai, Q. Sun, K. Cendrowski, H.-P. Meyer, Y. Vaynzof, E. Mijowska, J. Xiang and R. Klingeler, *RSC Adv.*, 2016, **6**, 76084–76092.
- 25 Z. Li, A. Ottmann, T. Zhang, Q. Sun, H.-P. Meyer, Y. Vaynzof, J. Xiang and R. Klingeler, *J. Mater. Chem. A*, 2017, **5**, 3987–3994.
- 26 G. Lian, C.-C. Tuan, L. Li, S. Jiao, K.-S. Moon, Q. Wang, D. Cui and C.-P. Wong, *Nano Lett.*, 2017, **17**, 1365–1370.
- 27 L. Li, B. Song, L. Maurer, Z. Lin, G. Lian, C.-C. Tuan, K.-S. Moon and C.-P. Wong, *Nano Energy*, 2016, **21**, 276–294.
- 28 D. Wei, Y. Liu, Y. Wang, H. Zhang, L. Huang and G. Yu, *Nano Lett.*, 2009, **9**, 1752–1758.
- 29 A. Manivel, G.-J. Lee, C.-Y. Chen, J.-H. Chen, S.-H. Ma, T.-L. Horng and J. J. Wu, *Mater. Res. Bull.*, 2015, **62**, 184–191.
- 30 H. Yang, X. Li, A. Wang, Y. Wang and Y. Chen, *Chin. J. Catal.*, 2014, **35**, 140–147.
- 31 E. Karabulut, T. Pettersson, M. Ankerfors and L. Wågberg, *ACS Nano*, 2012, **6**, 4731–4739.
- 32 R. A. Zangmeister, T. A. Morris and M. J. Tarlov, *Langmuir*, 2013, **29**, 8619–8628.
- 33 C. Zhao, J. Kong, L. Yang, X. Yao, S. L. Phua and X. Lu, *Chem. Commun.*, 2014, **50**, 9672–9675.
- 34 H. Lee, S. M. Dellatore, W. M. Miller and P. B. Messersmith, *Science*, 2007, **318**, 426–430.
- 35 K.-K. Liu, W. Zhang, Y.-H. Lee, Y.-C. Lin, M.-T. Chang, C.-Y. Su, C.-S. Chang, H. Li, Y. Shi, H. Zhang, C.-S. Lai and L.-J. Li, *Nano Lett.*, 2012, **12**, 1538–1544.
- 36 X.-D. Zhu, K.-X. Wang, D.-J. Yan, S.-R. Le, R.-J. Ma, K.-N. Sun and Y.-T. Liu, *Chem. Commun.*, 2015, **51**, 11888–11891.
- 37 Y. Zhang, K. Fugane, T. Mori, L. Niu and J. Ye, *J. Mater. Chem.*, 2012, **22**, 6575–6580.
- 38 K. Chang, D. Geng, X. Li, J. Yang, Y. Tang, M. Cai, R. Li and X. Sun, *Adv. Energy Mater.*, 2013, **3**, 839–844.
- 39 Y. Yu, C. Li, Y. Liu, L. Su, Y. Zhang and L. Cao, *Sci. Rep.*, 2013, **3**, 1866.
- 40 M.-R. Gao, M. K. Y. Chan and Y. Sun, *Nat. Commun.*, 2015, **6**, 7493.
- 41 J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan and Y. Xie, *J. Am. Chem. Soc.*, 2013, **135**, 17881–17888.
- 42 A. K. Geim and I. V. Grigorieva, *Nature*, 2013, **499**, 419–425.
- 43 F. Xiong, Z. Cai, L. Qu, P. Zhang, Z. Yuan, O. K. Asare, W. Xu, C. Lin and L. Mai, *ACS Appl. Mater. Interfaces*, 2015, **7**, 12625–12630.
- 44 L. Wang, Z. Xu, W. Wang and X. Bai, *J. Am. Chem. Soc.*, 2014, **136**, 6693–6697.
- 45 Z. Wan, J. Shao, J. Yun, H. Zheng, T. Gao, M. Shen, Q. Qu and H. Zheng, *Small*, 2014, **10**, 4975–4981.
- 46 N. He, L. Zhong, M. Xiao, S. Wang, D. Han and Y. Meng, *Sci. Rep.*, 2016, **6**, 33871.
- 47 Z. Zhu, Y. Tang, Z. Lv, J. Wei, Y. Zhang, R. Wang, W. Zhang, H. Xia, M. Ge and X. Chen, *Angew. Chem., Int. Ed.*, 2018, **57**, 3656–3660.
- 48 J.-Y. Hwang, H. M. Kim, S.-K. Lee, J.-H. Lee, A. Abouimrane, M. A. Khaleel, I. Belharouak, A. Manthiram and Y.-K. Sun, *Adv. Energy Mater.*, 2016, **6**, 1501480.
- 49 X.-Y. Yu, H. Hu, Y. Wang, H. Chen and X. W. Lou, *Angew. Chem., Int. Ed.*, 2015, **54**, 7395–7398.



- 50 V. Augustyn, J. Come, M. A. Lowe, J. W. Kim, P.-L. Taberna, S. H. Tolbert, H. D. Abruña, P. Simon and B. Dunn, *Nat. Mater.*, 2013, **12**, 518.
- 51 X. Wang, D. Chen, Z. Yang, X. Zhang, C. Wang, J. Chen, X. Zhang and M. Xue, *Adv. Mater.*, 2016, **28**, 8645–8650.
- 52 X. W. Lou and H. C. Zeng, *Chem. Mater.*, 2002, **14**, 4781–4789.
- 53 J. R. Kremer, D. N. Mastronarde and J. R. McIntosh, *J. Struct. Biol.*, 1996, **116**, 71–76.
- 54 D. N. Mastronarde, *J. Struct. Biol.*, 1997, **120**, 343–352.
- 55 D. N. Mastronarde and S. R. Held, *J. Struct. Biol.*, 2017, **197**, 102–113.
- 56 C. Neef, C. Jahne, H. P. Meyer and R. Klingeler, *Langmuir*, 2013, **29**, 8054–8060.

