


# Materials Advances

Volume 3  
Number 14  
21 July 2022  
Pages 5543–6072

[rsc.li/materials-advances](https://rsc.li/materials-advances)

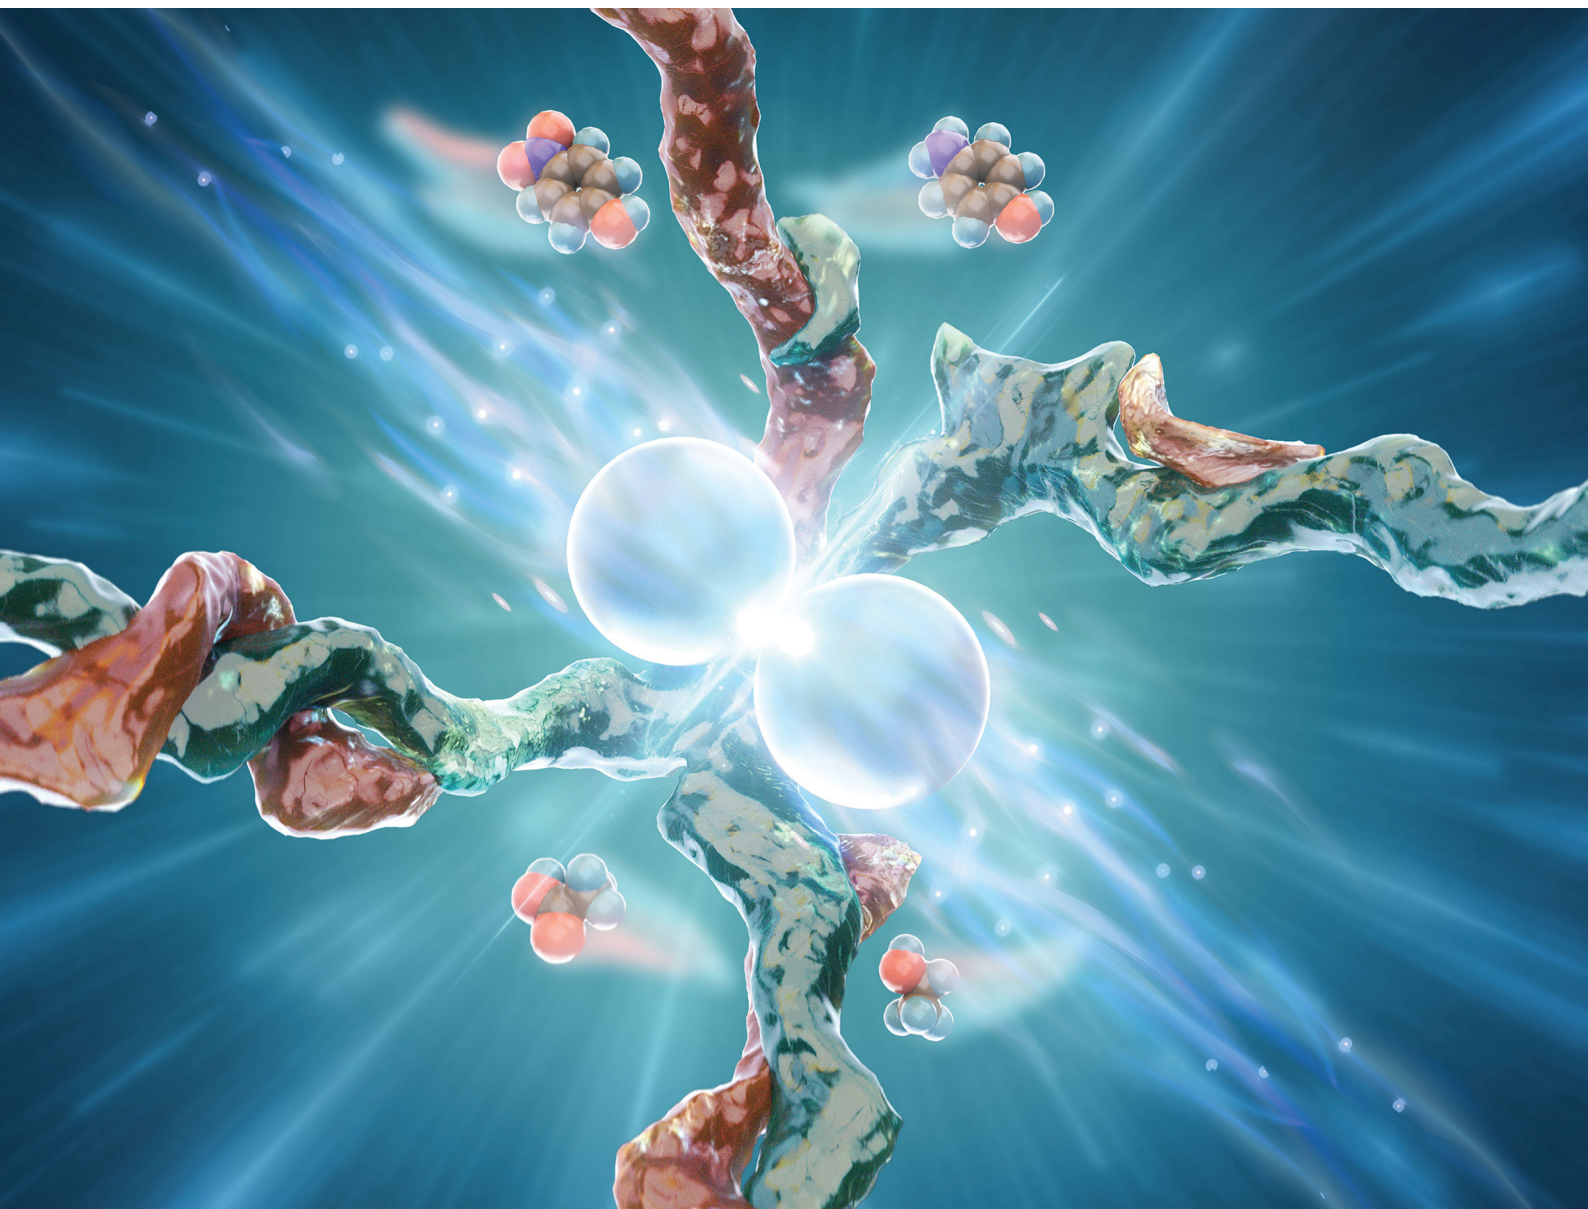

ISSN 2633-5409

**PAPER**

Alexander Eychmüller *et al.*  
Controllable electrostatic manipulation of structure building  
blocks in noble metal aerogels

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Mater. Adv.*, 2022,  
3, 5760Controllable electrostatic manipulation of  
structure building blocks in noble metal aerogels†Wei Wei, <sup>ab</sup> René Hübner, <sup>c</sup> Maximilian Georgi,<sup>a</sup> Cui Wang,<sup>a</sup> Xiaodong Wu<sup>d</sup> and  
Alexander Eychmüller <sup>\*a</sup>

The important role of structure homogeneity in three-dimensional network nanostructures serving as noble metal aerogels (NMAs) has attracted extensive attention in the field of electrochemistry in the last two decades, whereas a comprehensive study of tailoring skeleton units and element distributions in NMAs is still lacking. Herein, a new modulation strategy to easily prepare multiscale NMAs with tunable composition is developed by utilizing the electrostatic interaction between oppositely charged colloidal metal nanoparticles. The modulation rule of the chemical distribution in bimetallic aerogels leads to the construction of the as-tailored double skeleton aerogels for the first time. Considering their specific structures, the intrinsic and exceptional catalytic and electrocatalytic performances of NMAs were investigated. This study optimizes the structure homogeneity of noble metal aerogels by investigating nanoparticle–ligand interactions and provides further proof of their exceptional electrocatalytic capabilities.

Received 24th February 2022,  
Accepted 5th May 2022

DOI: 10.1039/d2ma00213b

[rsc.li/materials-advances](https://rsc.li/materials-advances)

## Introduction

Aerogels are self-supporting lightweight materials that contain highly porous multidimensional interconnected networks.<sup>1–3</sup> Due to the aerogel structure, these materials retain nanoscale properties at a macroscale and have extremely low density. In the past decades, tremendous advances have been made in synthesizing and developing novel aerogel materials from nanoparticles of oxides, semiconductors, carbon, polymers, and metals acting as building blocks for assembled networks.<sup>4–8</sup> In particular, noble metal aerogels (NMAs) have emerged as unique and attractive material platforms for multiple applications (e.g., catalysis, sensing, and surface-enhanced Raman scattering). The advantages of noble metals include a high electrical conductivity with a filled electron d-band. Additionally, due to the aerogel structure, they have a self-supported architecture with abundant active sites and electron/mass transfer pathways.<sup>9–11</sup> However, NMAs, as one of the newest members of the aerogel

family, were only discovered in 2009;<sup>12</sup> they are still in their infancy and will be extensively studied in the twenty-first century.<sup>3,11</sup>

The development of synthesis methodologies and the disclosure of the formation mechanisms of NMAs are a top priority. The sol–gel process is the typical method for NMA production. Specifically, this process refers to the fabrication procedure where wet hydrogels are formed by destabilization of building blocks to allow the gradual formation of continuous networks using steady nanoparticle solutions or molecular precursors. The gels are then dried by non-destructive drying methods (e.g., supercritical CO<sub>2</sub> drying or freeze drying) to become homogeneous aerogels. The triggering destabilization process is an important and difficult step in the fabrication of a broad range of NMA systems.<sup>11</sup> In previous studies, additional additives (such as oxidants, salts, and dopamine) were used to obtain gels.<sup>13–15</sup> Additionally, heating or freezing procedures as gelation-initiating operations have also been introduced in the NMA preparation.<sup>16–19</sup> However, many fundamental and operating difficulties remain, such as long gelation times in aqueous systems, time-consuming washing steps, and costly drying procedures in the NMA preparation. Recently, our group studied the NMA formation and developed the freeze–thaw strategy, the disturbance-promoted gelation method, and the excessive-reductant-directed gelation strategy.<sup>20–23</sup> Inspired by these significant advancements in the NMA preparation, it is necessary to regulate the structure formation of the building blocks or the skeleton units in the gel to further enhance the catalytic properties of NMAs.

Using the self-assembly of oppositely charged particles *via* electrostatic interactions, different nanoparticles (NPs) were

<sup>a</sup> Physical Chemistry, Technische Universität Dresden, Andreas-Schubert-Bau, Zellescher Weg 19, 01069 Dresden, Germany. E-mail: alexander.eychmueller@tu-dresden.de

<sup>b</sup> Center of Analysis and Test, School of Chemistry and Chemical Engineering, Jiangsu University, Xuefu Road 301, 212013 Zhenjiang, China


<sup>c</sup> Helmholtz-Zentrum Dresden-Rossendorf, Institute of Ion Beam Physics and Materials Research, Bautzner Landstrasse 400, 01328 Dresden, Germany

<sup>d</sup> College of Materials Science and Engineering, Nanjing Tech University, Puzhu South Road 30, 210009 Nanjing, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ma00213b>

In developing a feasible synthesis based on electrostatic interactions, the first step was to investigate oppositely charged noble metal particles as precursors. Due to the ligand chemistry in colloid solutions, an extensive range of ligand-stabilized gold NPs with different surface charges were obtained in prior studies.<sup>22</sup> The next objective was to develop a better understanding of electrostatic manipulation to prepare and modulate NMAs in a simple and novel process. Inspired by these empirical considerations, a simple and rapid method for the preparation of Au gels with tunable inner structures (ligament size = 10–30 nm) was developed by mixing oppositely charged gold NP solutions ( $C_M = 0.2\text{--}0.5\text{ mM}$ ) without further addition of the reagent, thus verifying the electrostatic homoaggregation approach. Next, an array of Au–Pd bimetallic aerogels with controlled ligament sizes were prepared by electrostatic heteroaggregation by mixing separately synthesized, oppositely charged gold and palladium NPs. Taking advantage of the non-reagent-triggered destabilization of this method than previous reports (Table S6, ESI<sup>†</sup>), we obtained bimetallic aerogels with double-skeleton structures and high specific surface areas ( $22.5\text{--}97.3\text{ m}^2\text{ g}^{-1}$ ) by adjusting the Au : Pd ratio. In addition, we found that, by replacing dopamine with polydopamine as a ligand for noble metal nanoparticles, the gold nanoparticle precursor mixed with other charged noble metal particles results in NMAs with smaller ligament sizes. Compared with the above-mentioned electrostatic manipulation, the average ligament sizes of Au in the NMAs decrease from 15.8 nm to 6.3 nm, and those of Pd in the NMAs decrease from 5.6 nm to 4.0 nm in the case of the dopamine assisted method. Notably, the catalytic reduction of *p*-nitrophenol and the ethanol oxidation reaction

The morphologies of the ligand-stabilized Au NPs and the final aerogels (obtained after freeze-drying) were examined

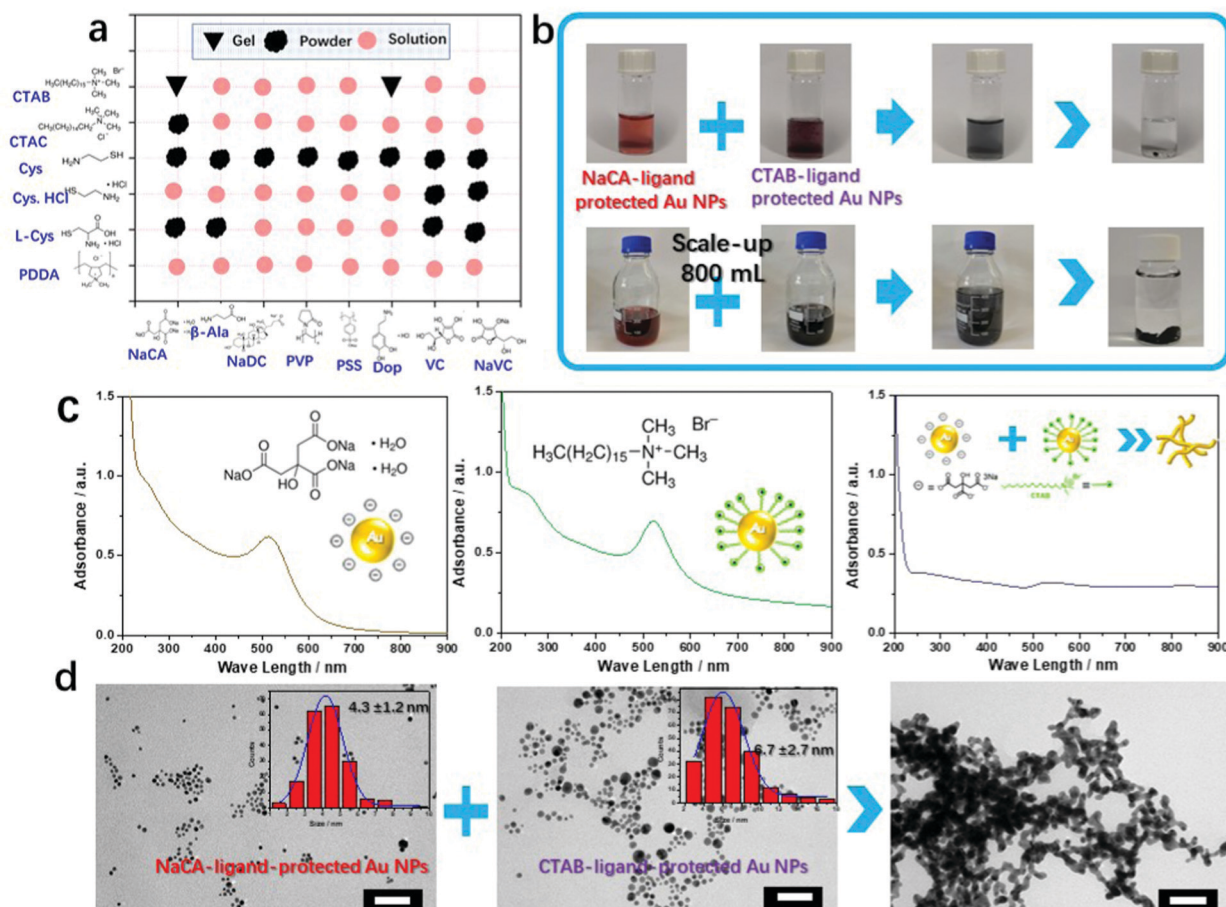

**Fig. 1** Fabrication process of gold gels by electrostatic interactions. (a) Summary of the status of gold gels induced by mixing of different ligand-stabilized gold NP solutions. The inverted triangle, diffused black circle, and pink circle represent the formation of a gel, powder, and stable colloidal solution, respectively. (b) Photographs of the synthesis of a gold aerogel using oppositely charged Au NP solutions ( $C_M = 0.2$  mM) by applying two different ligands (red: NaCA and purple: CTAB). (c) UV-vis absorption spectra of the Au NP solutions before and after mixing (inset: the proposed schematic gelation process). (d) TEM images and ligament size distributions (insets) of Au NPs fabricated in the presence of different ligands and the obtained gold aerogel. The scale bar in (d) is 50 nm.

using a transmission electron microscopy (TEM) (Fig. 1d). It was confirmed that there is no significant difference in the morphology and size distribution of the separately synthesized gold NPs. The negatively charged NaCA-stabilized ( $4.3 \pm 1.2$  nm) and positively charged CTAB-stabilized ( $6.7 \pm 2.7$  nm) gold NPs (with a quasi-spherical shape) form a porous gel structure consisting of interconnected Au NWs with an average ligament size of  $17.2 \pm 4.9$  nm. The larger diameter of the Au gel compared to that of the initial Au NPs can result from “less controlled” reaction conditions. Several Au NPs get in contact with each other more easily and they directly melt together to form bigger NPs due to the fusion of gold. Combining previous experience (freeze-thaw strategy, disturbance-promoted gelation method, *etc.*) with the present results, we conclude that the final porous gold gel assembles by gradual Au NP aggregation caused by attractive electrostatic interactions. The fusion of the soft Au oligomers is due to a competition between the growth and sedimentation of the Au aggregates.<sup>20–22</sup>

To understand the self-assembly behavior of the oppositely charged gold NPs by electrostatic co-aggregation, mixtures of

negatively charged NaCA-stabilized gold NPs and positively charged CTAB-stabilized gold NPs at different volume ratios (P/N) were characterized by zeta potential measurements. Fig. 2a shows the numerical results of the zeta potential in this mixed system. As the P/N ratio increases from 0.09 to 1.0, the zeta potential decreases and approaches almost zero, suggesting that the mixture is converted to a gold gel or aggregate. After the addition of abundant *p*-Au NPs into *n*-Au NPs (the P/N value increases from 2.0 to 11.0), the zeta potential becomes more positive again and the NP mixture remains stable as a colloidal solution. In particular, at P/N = 1, the zeta potential ( $\zeta$ ) of the CTAB-stabilized gold NPs (+27.7 mV) decreases to approximately 0 mV (measured value +1.5 mV) after adding the NaCA-stabilized gold NPs (−37.5 mV), indicating the neutralization of the surface charges. For P/N < 1, the zeta potential of the final solutions varies from +3 to +6 mV. For P/N > 1, the zeta potential increases again. Based on these observations, we investigated in more detail how different volume ratios affect the stability of the solution and the formation of the gel. To evaluate this mechanism, we performed density functional theory (DFT)

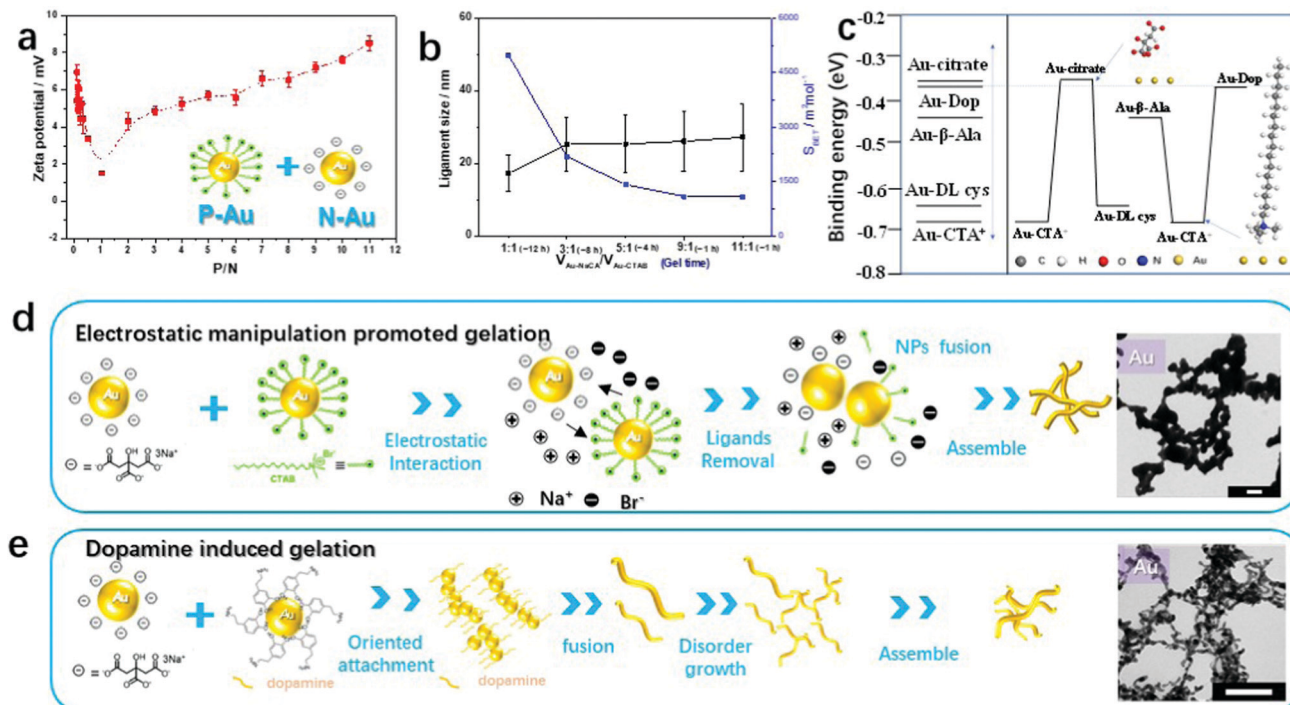


Fig. 2 Electrostatic manipulation and analysis of the Au gelation process. (a) Zeta potential of *p*-Au/*n*-Au mixtures in aqueous solution at different volume mixing ratios (P/N). (b) Ligament size and BET surface area values of Au aerogels prepared from different volume ratios of negatively and positively charged Au NPs. (c) DFT calculations. Left: Calculated binding energies ( $E_{\text{binding}}$ ) of different capping ligands adsorbed on the Au(111) surface. Right: A typical mixing process based on different capping ligands. Inset: Optimized structures of citrate and CTA<sup>+</sup> on the Au(111) surface. (d) Proposed schematic gelation mechanism induced by the electrostatic interaction of oppositely charged Au NPs. (e) Proposed schematic gelation mechanism induced by dopamine. The scale bars in (d) and (e) are 100 nm.

calculations to determine the binding energy ( $E_{\text{binding}}$ ) of the protonated forms of the ligands on the Au(111) surface (Fig. S4 and S5, ESI<sup>†</sup>), *i.e.* for cetyltrimethylammonium ions (CTA<sup>+</sup>) and citrate ions (CA<sup>-</sup>). As shown in Table S2 (ESI<sup>†</sup>), the binding energy of Au(111)-CTA<sup>+</sup> (−0.67 eV) is smaller than the binding energy of Au(111)-CA<sup>-</sup> (−0.36 eV), indicating a stronger interaction of the gold particle with CTA<sup>+</sup> compared to that with CA<sup>-</sup>. This suggests that the CTAB-stabilized gold NPs (*p*-Au NPs) are more stable than the NaCA-stabilized NPs (*n*-Au NPs). Therefore, if the amount of CTAB-stabilized gold NPs is high, the ligand can prevent the aggregation of the gold NPs due to the gold particles interacting with the ligand molecules. In contrast to the usual preparation of gold aerogels, the gelation time and BET surface values of the gold aerogels can be easily adjusted by this simple and convenient strategy of applying oppositely charged Au NP solutions of various volume ratios (Fig. 2b). By increasing the amount of the slightly smaller NaCA-stabilized Au NPs, the ligament size increases and consequently, the specific surface area of the gels decreases. One explanation for the increase in the ligament size is the higher mobility of smaller Au NPs, which causes them to aggregate in a less-ordered manner. Further studies are necessary to gain a deeper understanding of this aggregation behavior.

### Deeper insights into the electrostatic-manipulation-promoted gelation

To obtain a better understanding of the interaction of the charged nanoparticles and their ligands, we investigated the

mixed nanoparticle solutions and their products as shown in Fig. 1a and Fig. S2 (ESI<sup>†</sup>). From the experimental observations mentioned above, the mixing results of most ligands contain polymer functional groups, such as poly(diallyldimethylammonium chloride) solution (PDDA), polyvinylpyrrolidone (PVP), and poly(sodium-4-styrenesulfonate) (PSS), leading to stable colloidal gold NP solutions without precipitation. Due to their large size, the polymer ligands stabilize the gold nanoparticle solutions due to steric effects.<sup>22</sup> Most gold NP solutions containing thiolate-based ligands mixed with negatively charged gold NPs have undesirable effects on gelation. A few precipitates were found at the bottom of the vessel. The final products of these mixtures are shown in Fig. S6b, d, and e (ESI<sup>†</sup>). The high binding energy of a single thiol group on the Au NP surface (Au-S) prevents destabilization by oppositely charged particles. Due to the strong bonding, thiol based functionalized Au NPs remain in the colloidal state even when the oppositely charged Au NPs are added. Consequently, the color of the particle solution does not change and remains reddish.<sup>29,30</sup> Meanwhile, dopamine, as an initiator, triggers the formation of gold gels efficiently *via* electrostatic interactions. More than half of the different gold NP solutions are transformed into gels after mixing with dopamine-functionalized gold NP solutions (Fig. S6f, ESI<sup>†</sup>). This is similar to previous reports of a dopamine-based method that can construct NMAs with a special oriented attachment mechanism.<sup>15,31</sup> Due to the complex and diverse roles of dopamine during the gelation, we will discuss this special case in the next chapter.

To further investigate the mechanism of the electrostatic-manipulation-promoted gelation and support our assumptions, we carried out DFT calculations to evaluate the binding energy ( $E_{\text{binding}}$ ) of the protonated form of CTAB on the Au surface. We compared these results with other capping ligands such as NaCA,  $\beta$ -Ala, and L-cysteine (Fig. S10–S12, ESI<sup>†</sup>). As shown in Fig. 2c and Table S1 (ESI<sup>†</sup>), the  $E_{\text{binding}}$  increases in the order of Au(111)–CTA<sup>+</sup> (−0.67 eV) < Au(111)–L-Cys (−0.65 eV) < Au(111)– $\beta$ -Ala (−0.43 eV) < Au(111)–CA<sup>−</sup> (−0.36 eV). Based on this comparison, the long-branched chain of CTA<sup>+</sup> and the Au–S bonds from the thiolate-bond ligands such as cysteamine (Cys), cysteamine hydrochloride (Cys-HCl), and L-cysteine hydrochloride (L-Cys) prevent the formation of aggregated structures and thus maintain the gold NP stability. As described above, the CTAB-stabilized gold NPs behaved differently in the actual experiment. They can be easily destabilized by mixing with NaCA-stabilized gold NPs. We speculate that another component of the surfactant CTAB, in particular the halide ion (Br<sup>−</sup>), could play a significant role. Our recent work disclosed detailed mechanisms regarding the specific ion effects to explain the gelation process and showed a cation-directed manipulation mechanism for controlling the

Combining the above results and previous studies, we suggest the gelation mechanism of oppositely charged colloidal gold NP solutions as follows (Fig. 2d): (i) the negative gold NPs instantly approach the positive gold NPs because of the electrostatic interaction. (ii) The  $\text{Br}^-$  ions from the CTAB-stabilized gold NPs replace a few citrate ions from the NaCA-stabilized gold NPs. The ligand-replaced gold particles, especially with halide ions  $\text{Br}^-$ , are unstable compared with the original gold NPs that are characterized by oppositely charged ions. (iii) Metal aggregation continuously occurs by fusing gold NPs with free surface gold NPs to achieve a lower surface energy. (iv) The aggregation process is repeated and more Au NWs are successively formed to assemble randomly in a three-dimensional network. (v) Hydrogel precipitation at the bottom of the reaction flask is caused by the gravitational settlement of the particles and network multi-aggregates. This gelation process is similar to previously suggested gelation mechanisms, such as the salting-out-assisted mechanism for NMAs.<sup>29</sup> The significant difference lies in the addition of a salt to obtain oppositely charged particles in the latter case. In the gelation process reported here, the addition of a salt to a colloidal solution is no longer necessary, since the mixing of oppositely charged solutions directs and initiates gelation. In addition to fewer reaction steps and a short gelation time leading to the cost reduction of the gel preparation, the follow-up washing time for hydrogel cleaning is also reduced compared to the excessive-reductant-directed gelation strategy.

In the following, we focus on the strong and effective gelation support by the dopamine molecule, which was observed in the above-mentioned gelation overview of oppositely charged Au NPs (Fig. 1a and Fig. S3, ESI<sup>†</sup>). In previous studies, we demonstrated the synthesis of Au aerogels *via* a dopamine-induced route, where the Au aerogels are composed of 3D nanowire networks with diameters of 5–6 nm.<sup>15</sup> Zhu *et al.* introduced a facile synthetic strategy to form polydopamine (PDA)-capped AuPt hydrogels using a one-step method.<sup>31</sup> Meanwhile, PDA-coated gold nanoparticles could be synthesized with diverse morphologies depending on the dopamine concentration including aggregated NPs, almost monodisperse NPs, and NP chains.<sup>38</sup> Dopamine acts not only as a ligand stabilizer but also as a gelation trigger depending on the reaction environment. Interestingly, we found an analogous gelation phenomenon for ligand-stabilized gold NPs mixed with a gold NP solution in the presence of dopamine (*e.g.* Au-CA + Au-Dop), as revealed by real-time observations. The gelation process was observed by *in situ* optical microscopy (Movie S2 and Fig. S13c, ESI<sup>†</sup>) and was similar to the above-mentioned gelation process. According

Both the morphology and ligament size of the gold gels are strongly influenced by the P/N ratio in the CTAB/NaCA hybrid system *via* electrostatic manipulation, as previously demonstrated (Fig. S15, ESI<sup>†</sup>). When the concentration of CTAB in the final mixture decreases (Fig. S15a and b, ESI<sup>†</sup>), the ligament size increases by *ca.* 10 nm. Because the Br<sup>−</sup> ions from CTAB partially coat the Au NPs, forming close-packed aggregates with little fusion, high Br<sup>−</sup> ion concentrations can prevent the fusion of the aggregates.<sup>32</sup> If dopamine is involved in the synthesis of the gold aerogel (Fig. S15c and d, ESI<sup>†</sup>), it plays a critical role in controlling the metal structure. The results of the comparative study show that the dopamine-assisted method yields a smaller ligament size ( $5.7 \pm 1.1$  nm) of gold aerogels compared to the CTAB/NaCA hybrid system method (Table S3, ESI<sup>†</sup>). This causes the gold aerogel to have a high surface area of  $57.4 \text{ m}^2 \text{ g}^{-1}$ . Because the ligament size also affects other porosity-related properties such as the specific surface area, the pore volume, and the pore size distribution, N<sub>2</sub>-physisorption experiments were performed for the samples (Fig. S16 and Table S3, ESI<sup>†</sup>). The measured isotherms are similar to each other and exhibit a typical NMA-like behavior,<sup>20–22</sup> *i.e.* a mixture of type II and IV isotherms, which is caused by the broad pore size distributions. The aerogels are composed of micro-, meso-, and macropores. As expected, both the specific surface area and total pore volume decrease with the increasing ligament size. In summary, the simple mixing of oppositely charged NP solutions is a promising approach for achieving controlled Au aerogel architectures (ligament sizes ranging from  $\sim 6$  nm to 30 nm). It is possible to convert nanoparticles to gels by simply mixing different ligand-stabilized gold NPs.

### Fabrication of Au–Pd aerogels by two gelation processes and their characterization


### Further characterization of the gold aerogels

The crystalline structure of the gold aerogels obtained by the electrostatic interaction and dopamine-induced gelation was further characterized by X-ray diffraction (XRD). As shown in Fig. S14 (ESI<sup>†</sup>), the dominant peaks at 38.2°, 44.3°, 64.6°, 77.5°, and 81.7° demonstrate the crystalline nature of the gold aerogels and correspond to the diffraction from the (111), (200), (220), (311), and (222) planes of face-centered-cubic metallic gold (PDF#04-0784). The difference in the final ligament size of the gels was further confirmed by XRD for the homologous samples, where the diffraction peaks broaden with the decreasing

S18b, ESI† and Movies S3 and S4, ESI†) recorded *in situ* during gelation.

The negatively charged gold NPs and positively charged palladium NPs were mixed to obtain unordered, gel-like three-dimensional networks. To modulate the ligament size of the Au–Pd aerogels, mixtures of NaCA-stabilized gold NPs and CTAB-stabilized palladium NPs at different volume mixing ratios were investigated. Since the TEM images of the Au–Pd gels (Fig. S17b, ESI†) show two different ligament sizes in the gel structure, a strong indication for the separation of both metals and the element distribution of gold and palladium were analyzed. From the high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) images and the corresponding energy-dispersive X-ray spectroscopy (EDX)-based element distributions in Fig. S19 (ESI†), the formation of a double-skeleton structure in the Au–Pd aerogel is deduced. The two metals do not form an alloy, which was typically observed in previous studies.<sup>23</sup> More details about the double-skeleton structure are provided by the EDX data in Fig. 3a and b. The separation of the Au and Pd NPs is observed for both synthesis routes: electrostatic manipulation-promoted

gelation and dopamine-induced gelation. Both types of metal nanoparticles form separated gel networks, which are intertwined. Nevertheless, the separated gels share crosslinks at which they are interconnected. If one of the metals is added to a small percentage of the second metal, these metal NPs tend to become incorporated into the 3D network metal gel as a respective metal part. As in the case of the monometallic gold gels, the mixing ratio of the *n*-Au NPs and *p*-Pd NPs plays a crucial role in the bimetallic gel morphology and influences the ligament size of the gels. If the concentration of the gold solution is high (e.g. for Au1Pd1), the Au part forms large ligaments with a size of *ca.* 15 nm. This is in contrast with the small ligament sizes of *ca.* 8 nm for high concentrations of palladium NPs (e.g. for Pd9Au1). Additionally, the morphological features of the Au–Pd aerogel with a molar ratio of 1 : 1 in NaCA/CTAB (Fig. 3a) and NaCA/Dop (Fig. 3b) can be compared in detail. Under the influence of dopamine, smaller ligaments (Au ligament size:  $6.3 \pm 1.8$  nm and Pd ligament size:  $4.0 \pm 1.2$  nm) are observed in bimetallic aerogels compared to the electrostatic-manipulation-promoted synthesis route (Au ligament size:  $15.7 \pm 4.6$  nm and Pd ligament size:  $5.5 \pm 1.4$  nm). Similar to

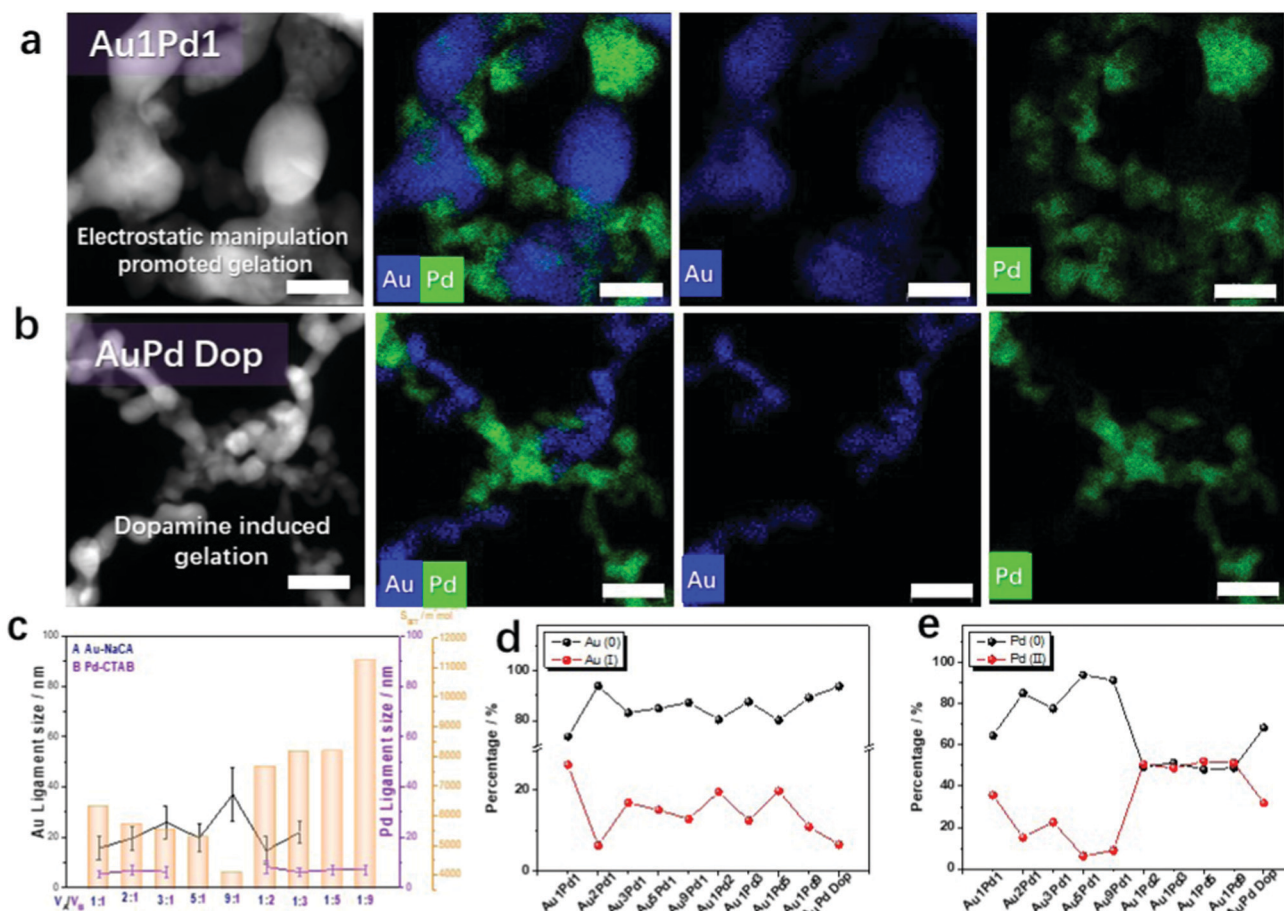

**Fig. 3** Electrostatic manipulation and analysis of Au–Pd gels. (a and b) HAADF-STEM images and EDX-based element distributions of Au–Pd aerogels from two gelation processes: electrostatic-manipulation-promoted gelation (a) and dopamine-induced gelation (b). The scale bars in the HAADF-STEM images and element distributions are both 20 nm. (c) Ligament sizes and BET surface area values of the Au–Pd aerogels prepared from different volume ratios of negatively charged Au NPs and positively charged Pd NPs. (d and e) Valence-state fractions of gold and palladium for Au–Pd aerogels synthesized by the two gelation processes as derived by deconvolution of the corresponding XPS spectra.



X-Ray photoelectron spectroscopy (XPS) was used to determine the valence states of the synthesized Au-Pd aerogels. As shown in Fig. S23-S25 (ESI<sup>†</sup>), both Au and Pd feature various valence states, which can be proven by the presence of oxygen in the spectra and the deconvolution of the high-resolution XPS spectra. By integrating the corresponding peak areas of the high-resolution XPS spectra,<sup>40</sup> the relative contents of the Au and Pd species in the Au-Pd aerogels were calculated and are summarized in Fig. S3d and e (ESI<sup>†</sup>). With the increasing Au

Due to their intriguing physicochemical properties, NMAs have been extensively employed in diverse applications. However, the effects of the ligament size and the element distribution on catalytic performance have been scarcely studied. To evaluate the catalytic activity of the Au and Au-Pd aerogels with different ligament sizes and element compositions, the chemical reduction of *p*-nitrophenol (*p*-NP) to *p*-aminophenol (*p*-AP) and the electrocatalytic alcohol electro-oxidation reaction (EOR) were selected as model reactions. For the reduction of *p*-NP, typical reaction-time-dependent UV-vis absorption spectra are shown in Fig. 4a, b, and Fig. S26 (ESI<sup>†</sup>). For this catalytic reaction, we used Au aerogels prepared by dopamine-induced gelation and Au<sub>1</sub>Pd<sub>X</sub> (*X* = 1, 3, 5, 9) aerogels obtained by electrostatic-manipulation-promoted gelation. These aerogels were chosen due to their good dispersion in solution, smallest ligament sizes and highest specific surface areas, which are important factors for the catalytic activity. A small amount of Au or Au<sub>1</sub>Pd<sub>X</sub> (20 μL, 0.5 mg mL<sup>-1</sup>) converts *p*-NP to *p*-AP within 200 s. This is shown by the decreasing intensity of the peak maximum of *p*-NP and the increasing intensity of the peak maximum of *p*-AP (Fig. 4a and b). Over 95% of the *p*-NP is reduced by Au and Au-Pd aerogels with ligament sizes below 8 nm, while the Au aerogel using β-alanine-stabilized NPs has low activity because of the excessive polymer ligands on the metal surface, inhibiting the interaction between the substrates and reactive sites (Fig. S15d, ESI<sup>†</sup>). The catalytic performance of the Au-Pd aerogels with different compositions was also investigated. The catalytic conversion efficiency of the Au-Pd aerogels progressively increases with the increasing Pd content, revealing the high catalytic activity of palladium. In particular, the efficiency after 60 s was relatively low for Au<sub>1</sub>Pd<sub>1</sub> (72.6%) and the highest for Au<sub>1</sub>Pd<sub>9</sub> (98.2%). Apart from the influence of the chemical composition on the catalytic activity, the ligament

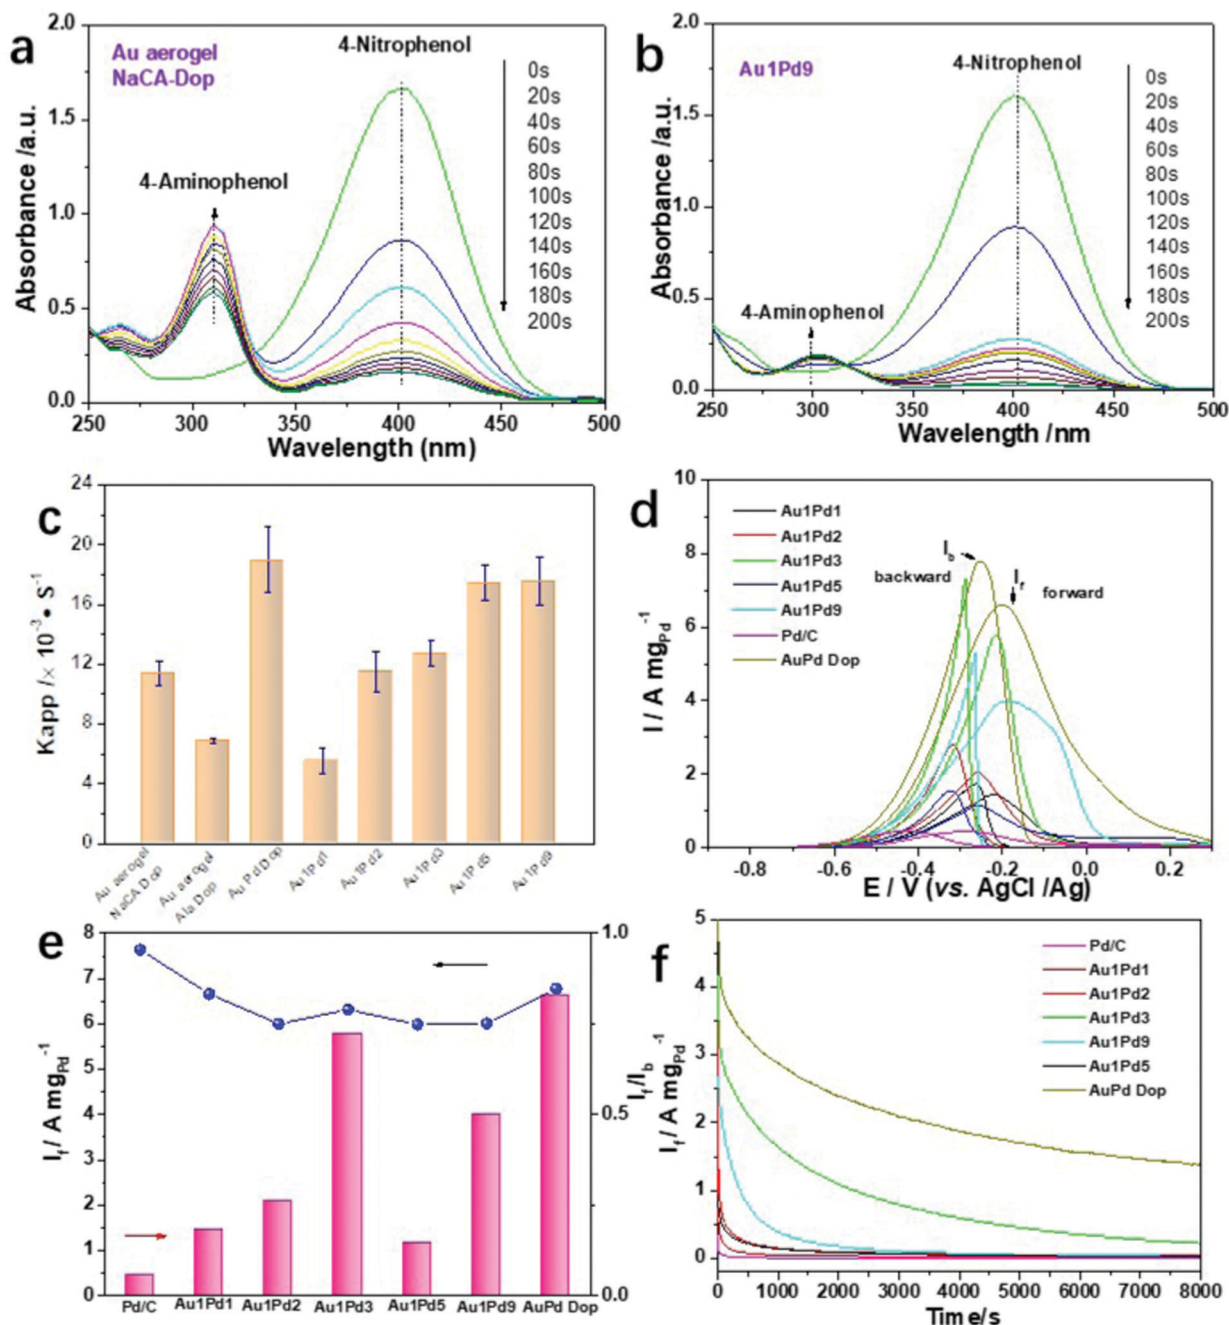


Fig. 4 Various applications of Au–Pd aerogels in chemical catalysis and electrocatalysis. (a and b) Time-dependent UV-vis spectra of the reduction of *p*-nitrophenol for the Au and Au1Pd9 aerogels. (c) Comparison of the apparent rate constant of Au and Au–Pd aerogels with different Au/Pd molar ratios. (d) Cyclic voltammetry curves of the ethanol electro-oxidation with various Au–Pd aerogel catalysts and commercial Pd/C. (e) Summarized  $I_f$  and  $I_f/I_b$  of various Au–Pd aerogels and Pd/C. (f) Chronoamperometry curves of different Au–Pd aerogel catalysts and commercial Pd/C.

size is another important factor in the reduction reaction. For bimetallic aerogels, larger apparent rate constants ( $k_{app}$ ) were obtained for gels with smaller ligament sizes (Fig. 4c). The  $k_{app}$  values were calculated to be  $5.57 \text{ s}^{-1}$  and  $17.57 \text{ s}^{-1}$  in the case of Au1PdX ( $X = 1$  and  $9$ , respectively). Intriguingly, increasing the Pd content in bimetallic aerogels indicated a larger ligament size of palladium, but an obvious decrease in the gold ligament size was still observed, reflecting that these smaller particles still dominated the catalysis process. Similarly, the catalytic

performance of the corresponding plots of  $-\ln(A_t/A_0)$  versus time is shown in Fig. S26d–h (ESI†). The  $-\ln(A_t/A_0)$  values show a linear correlation, revealing that the chemical reduction follows a first-order reaction law. More importantly, the AuPd dopamine-promoted (Dop) aerogel shows the highest catalytic activity (efficiency 98.4%), which is three times higher than that of the Au1Pd1 aerogel using oppositely charged NP solutions of the same ratio. This observation further confirms the high catalytic activity of aerogels having a small ligament size.

negative charges of the metal NPs (Au and Pd) were characterized by measuring their zeta potentials. Notably, these methods produce monometallic gold aerogels with widespread ligament sizes (5.7 to 27.2 nm) and corresponding specific surface areas (5.5 to 57.4 m<sup>2</sup> g<sup>-1</sup>). Bimetallic aerogels with extensively tunable compositions (*e.g.*, Au-Pd), variable ligament sizes (5.6 to 37.0 nm), and specific surface areas (22.5 to 97.3 m<sup>2</sup> g<sup>-1</sup>) were also obtained. Furthermore, these new synthetic approaches (electrostatic-manipulation-promoted gelation or dopamine-induced gelation) led to the formation of double-skeleton-like twined gel structures, where both elements form separated gel networks. Finally, utilizing the unique chemical properties and element adjustability of nanostructured noble metals, the chemical reduction of *p*-nitrophenol to *p*-aminophenol and the electrocatalytic ethanol oxidation were studied. The small ligament sizes and large specific surface areas increased the catalytic performance of the gels due to the presence of more active sites in the nanostructured network. Therefore, the present work not only establishes a novel and simple method to synthesize various single-/bimetallic noble metal aerogels with artificially controlled element distribution (*e.g.*, double-skeleton structure) but also offers a new level for developing high-performance (electro)-catalysts by making the most favorable and size distribution.

## Experimental procedures

## Synthesis procedures

NMAs were synthesized at ambient temperature ( $\sim 293$  K). A specific amount of ligand, noble metal salts, and  $\text{NaBH}_4$  were sequentially added to deionized water under stirring. The molar ratios of the metal salt (M), ligand (L), and reductant (R) were fixed at  $1/10/4$ .<sup>21,22,29</sup> The as-prepared noble metal nanoparticle solution was mixed for 10 min. Colloidal hydrogels were formed by mixing positively charged and negatively charged gold NP solutions in a volume ratio of 1 : 1. After grinding for  $\sim 12$  h, a monolithic gel was obtained. The fabrication process can be readily scaled up to 800 mL using the same procedure. The as-prepared hydrogel was washed with water five times before solvent exchange with tert-butanol. After being flash-frozen and freeze-dried for 24 h, the corresponding aerogel was obtained. For AuPd gels, the procedure was analogous to the synthesis described above; only a Pd NP solution was used instead of a second Au NP solution. Further experimental details can be found in the ESI.<sup>†</sup>

### Catalytic reduction

The catalytic performance of the NMAs was evaluated by the reduction of *p*-nitrophenol at room temperature. All aqueous solutions were freshly prepared. A standard catalytic test reaction was carried out in a quartz glass cuvette. For the catalytic reduction of *p*-NP, 30  $\mu\text{L}$  of *p*-NP (10 mM) and 150  $\mu\text{L}$  of  $\text{NaBH}_4$  (2 M) were added to a quartz glass cell containing 2.97 mL of deionized water. Thereafter, 20  $\mu\text{L}$  of an aqueous solution containing the aerogel catalyst (0.5 mg  $\text{mL}^{-1}$ ) were injected

## Summary

Diverse challenges (such as long gelation times, time-consuming washing operations, and costly procedures) in the synthesis of NMAs hinder their dissemination and the optimization of their potential applications. Utilizing the surface charge neutralization, the self-healing behavior of noble metal aggregates and the effect of destabilization in the mixture, an electrostatic manipulation method has been presented by directly mixing oppositely charged noble metal nanoparticle solutions to prepare the corresponding noble metal hydrogels (Au and Au-Pd, with metal salt concentrations  $C_M = 0.2$  to  $0.5$  mM) without introducing additional reagents. Additionally, mixing ligand-stabilized gold NPs with dopamine-coated gold NPs is a convenient way to obtain hydrogels. The differently charged metal NPs were obtained by simple functionalization with different ligands during the reduction of the metal salts. The positive and

Training Program of Jiangsu University, and the High-Performance Computing Center of Nanjing Tech University.

## References

All electrochemical tests were performed using an electrochemical workstation in a three-electrode system. A platinum foil and an Ag/AgCl (saturated KCl aqueous solution) electrode were used as the counter and reference electrodes, respectively. A glassy carbon electrode (GCE, diameter = 3 mm) was chosen as the substrate for holding the catalysts. For the electro-oxidation of ethanol, the performance was measured in an N<sub>2</sub>-saturated 1.0 M KOH aqueous solution containing 1.0 M ethanol. Further details regarding the procedure can be found in the ESI.†

## Author contributions

Wei: writing – original draft, methodology, data curation, and conceptualization. René Hübner: data curation, investigation, and writing – review and editing. Maximilian Georgi: data curation, conceptualization, and writing – review and editing. Cui Wang: validation, investigation, and writing – review and editing. Xiaodong Wu: software, investigation, and writing – review and editing. Alexander Eychmüller: supervision, funding acquisition, and writing – review and editing.

## Data and software availability

All data needed to evaluate the conclusions in the paper are present in the paper and/or the ESI.† Additional data related to this paper can be requested from the authors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors thank Dr Nelli Weiß, Susanne Goldberg, and Ankita Bora for TEM measurements; Linlin Wang, Dr Juliane Simmchen, and Sharan Priyanka for optical imaging and zeta potential measurements; Daniel Spittel for electrochemical measurements and Dr Ran Du and Dr Xuelin Fan for helpful discussions. The use of the HZDR Ion Beam Center TEM facilities and the funding of TEM Talos by the German Federal Ministry of Education and Research (BMBF; grant No. 03SF0451) in the framework of HEMCP are acknowledged. The authors would like to thank Weiwei Wang from Shiyanjia Lab ([www.shiyanjia.com](http://www.shiyanjia.com)) for the XPS analysis. This work was supported by the Swiss National Science Foundation (SNF), the German Research Foundation (DFG EY 16/18-2), the National Natural Science Foundation of China (21607063), the Jiangsu Overseas Visiting Scholar Program for University Prominent Young & Middle-aged Teachers and Presidents, the Outstanding Chinese and Foreign Youth Exchange Program of the China Association for Science and Technology (CAST), the Youth Talent

- 1 N. Hüsing and U. Schubert, *Angew. Chem., Int. Ed.*, 1998, **37**, 22–45.
- 2 C. Ziegler, A. Wolf, W. Liu, A.-K. Herrmann, N. Gaponik and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2017, **56**, 13200–13221.
- 3 X. Jiang, R. Du, R. Hübner, Y. Hu and A. Eychmüller, *Matter*, 2021, **4**, 54–94.
- 4 S. Kistler, *Nature*, 1931, **127**, 741.
- 5 J. Mohanan, I. Arachchige and S. Brock, *Science*, 2005, **307**, 397–400.
- 6 H. Sun, X. Zhen and C. Gao, *Adv. Mater.*, 2013, **25**, 2554–2560.
- 7 B. Cai, V. Sayevich, N. Gaponik and A. Eychmüller, *Adv. Mater.*, 2018, **30**, 1707518.
- 8 Q. Zheng, L. Fang, H. Guo, K. Yang, Z. Cai, M. Meador and S. Gong, *Adv. Funct. Mater.*, 2018, **28**, 1706365.
- 9 R. Du, X. Fan, X. Jin, R. Hübner, Y. Hu and A. Eychmüller, *Matter*, 2019, **1**, 39–56.
- 10 B. Cai and A. Eychmüller, *Adv. Mater.*, 2019, **31**, 1804881.
- 11 R. Du, X. Jin, R. Hübner, X. Fan, Y. Hu and A. Eychmüller, *Adv. Energy Mater.*, 2020, **10**, 1901945.
- 12 N. C. Bigall, A. K. Herrmann, M. Vogel, M. Rose, P. Simon, W. Carrillo-Cabrera, D. Dorfs, S. Kaskel, N. Gaponik and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2009, **48**, 9731–9734.
- 13 W. Liu, A. K. Herrmann, D. Geiger, L. Borchardt, F. Simon, S. Kaskel, N. Gaponik and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2012, **51**, 5743–5747.
- 14 K. G. Ranmohotti, X. Gao and I. U. Arachchige, *Chem. Mater.*, 2013, **25**, 3528–3534.
- 15 D. Wen, W. Liu, D. Haubold, C. Zhu, M. Oschatz, M. Holzschuh, A. Wolf, F. Simon, S. Kaskel and A. Eychmüller, *ACS Nano*, 2016, **10**, 2559–2567.
- 16 B. Cai, D. Wen, W. Liu, A. K. Herrmann, A. Benad and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2015, **54**, 13101–13105.
- 17 C. Zhu, Q. Shi, S. Fu, J. Song, H. Xia, D. Du and Y. Lin, *Adv. Mater.*, 2016, **28**, 8779–8783.
- 18 H. L. Gao, L. Xu, F. Long, Z. Pan, Y. X. Du, Y. Lu, J. Ge and S. H. Yu, *Angew. Chem., Int. Ed.*, 2014, **53**, 4561–4566.
- 19 A. Freytag, S. Sánchez-Paradinas, S. Naskar, N. Wendt, M. Colombo, G. Pugliese, J. Poppe, C. Demirci, I. Kretschmer, D. W. Bahnemann, P. Behrens and N. C. Bigall, *Angew. Chem., Int. Ed.*, 2016, **55**, 1200–1203.
- 20 R. Du, J.-O. Joswig, R. Hübner, L. Zhou, W. Wei, Y. Hu and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2020, **59**, 8293–8300.
- 21 R. Du, J.-O. Joswig, X. Fan, R. Hübner, D. Spittel, Y. Hu and A. Eychmüller, *Matter*, 2020, **2**, 908–920.
- 22 R. Du, J. Wang, Y. Wang, R. Hübner, X. Fan, I. Senkovska, Y. Hu, S. Kaskel and A. Eychmüller, *Nat. Commun.*, 2020, **11**, 1590.



- 23 X. Fan, S. Zerebecki, R. Du, R. Hübner, G. Marzum, G. Jiang, Y. Hu, S. Barcikowski, S. Reichenberger and A. Eychmüller, *Angew. Chem., Int. Ed.*, 2020, **59**, 5706–5711.
- 24 M. E. Leunissen, C. G. Christova, A. P. Hynninen, C. P. Royall, A. I. Campbell, A. Imhof, M. Dijkstra, R. Van Roij and A. Van Blaaderen, *Nature*, 2005, **437**, 235–240.
- 25 J. Kolny, A. Kornowski and H. Weller, *Nano Lett.*, 2002, **2**, 361–364.
- 26 S. Zhang, Y. Shao, G. Yin and Y. Lin, *Angew. Chem., Int. Ed.*, 2010, **49**, 2211–2214.
- 27 S. Wintzheimer, T. Granath, M. Oppmann, T. Kister, T. Thai, T. Kraus, N. Vogel and K. Mandel, *ACS Nano*, 2018, **12**, 5093–5120.
- 28 D. Wen, A.-K. Herrmann, L. Borchardt, F. Simon, W. Liu, S. Kaskel and A. Eychmüller, *J. Am. Chem. Soc.*, 2014, **136**, 2727–2730.
- 29 R. Du, Y. Hu, R. Hübner, J.-O. Joswig, X. Fan and A. Eychmüller, *Sci. Adv.*, 2019, **5**, eaaw4590.
- 30 J. Beurton, P. Lavalley, A. Pallotta, T. Chaigneau, I. Clarot and A. Boudier, *Int. J. Pharm.*, 2020, **580**, 119244.
- 31 Y. Wu, L. Jiao, W. Xu, W. Gu, C. Zhu, D. Du and Y. Lin, *Small*, 2019, **15**, 1900632.
- 32 Z. Zhang, H. Li, F. Zhang, Y. Wu, Z. Guo, L. Zhou and J. Li, *Langmuir*, 2014, **30**, 2648–2659.
- 33 L. Kühn, A. K. Herrmann, B. Rutkowski, M. Oezaslan, M. Nachtegaal, M. Klose, L. Giebeler, N. Gaponik, J. Eckert and T. J. Schmidt, *Chem. – Eur. J.*, 2016, **22**, 13446–13450.
- 34 M. Oezaslan, A. K. Herrmann, M. Werheid, A. I. Frenkel, M. Nachtegaal, C. Dosche, C. L. Bonnaud, H. C. Yilmaz, L. Kühn, E. Rhiel, N. Gaponik, A. Eychmüller and T. J. Schmidt, *ChemCatChem*, 2017, **9**, 798–808.
- 35 L. Jiao, W. Xu, H. Yan, Y. Wu, W. Gu, H. Li, D. Du, Y. Lin and C. Zhu, *Chem. Commun.*, 2019, **55**, 9865–9868.
- 36 Z. Liao, W. Zhang, Z. Qiao, J. Luo, A. Erpuding, A. Niwaer, X. Meng, H. Wang, X. Li, F. Zuo and Z. Zhao, *J. Colloid Interface Sci.*, 2020, **562**, 81–90.
- 37 A. Freytag, M. Colombo and N. C. Bigall, *Z. Phys. Chem.*, 2017, **231**, 63–75.
- 38 K. H. Samuel, Sy, L. W. Cola, Ho, W. C. Yu Lau, H. Ko and C. H. Jonathan Choi, *Langmuir*, 2018, **34**(46), 14033–14045.
- 39 U. Holzwarth and N. Gibson, *Nat. Nanotechnol.*, 2011, **6**, 534.
- 40 R. Du, W. Jin, R. Hübner, L. Zhou, Y. Hu and A. Eychmüller, *Adv. Energy Mater.*, 2020, **10**, 1903857.

